

(METRIC)  
A-A-3108A  
May 15, 1997  
SUPERSEDING  
A-A-3108  
March 25, 1977

## COMMERCIAL ITEM DESCRIPTION

### TINTING MEDIUM, ENAMEL: UNIVERSAL COLORANTS

The General Services Administration has authorized the use of this commercial item description for all federal agencies.

#### 1. SCOPE.

This commercial item description covers universal tinting medium dispersions and concentrates used primarily for tinting different types of interior and exterior paints.

#### 2. CLASSIFICATION. The colors covered by this commercial item description shall be the following:

1a	Carbon Black
2a	Phthalocyanine Blue
3a	Burnt Sienna
3b	Burnt Umber
3c	Raw Sienna
3d	Raw Umber
4b	Phthalocyanine Green
5b	Hansa Orange
6a	Bright Red Iron Oxide
7b	Hansa Yellow

#### 3. SALIENT CHARACTERISTICS.

**3.1 General properties.** The concentrates and dispersions shall consist of well ground pigments mixed with a suitable liquid solution. The concentrates and dispersions shall be dispersible in both alkyl and water based interior and exterior paints coatings.

**3.1.1 Stability.** The concentrate, as received, shall show no evidence of settling, gelling, or caking.

**3.1.2 Prohibited materials.** The manufacturer shall certify that no mercury, cadmium, hexavalent chromium, or Ozone Depleting Substances (ODSs) are used in the formulation. Except for carbon black, known or suspected human carcinogens, (as defined by the National Toxicology Program's (NTP) Annual Report on Carcinogens), also shall not be used in the formulation. If any of these substances are present as impurities in a raw ingredient, their concentration shall be less than 1.0 percent by weight. The lead content of the nonvolatile portion of the concentrate or dispersion shall not exceed 0.06 percent.

**3.1.3 Condition in container.** The colorant shall be free from seeds and hard settled pigment. It shall be readily dispersible to a uniform condition by five minutes of hand stirring.

Beneficial comments, recommendations, addition, deletions, clarifications, etc. and any data which may improve this document should be sent to: General Services Administration, Paints and Chemicals Commodity Center, Engineering and Commodity Management Division (10FTE), 400 15th St. SW, Auburn, WA. 98001.

## A-A-3108 A

**3.1.4 Accelerated storage stability.** When tested as specified in ASTM D 1849, the concentrate shall not be caked, livered, skinned, or show evidence of putrefaction.

**3.2 Special requirements:**

**3.2.1 Color.** The color of the concentrate shall be characteristic of the prime pigment specified in table I.

**3.2.2 Odor.** The odor shall not be obnoxious, disagreeable, or offensive, when tested in accordance with ASTM D 1296.

**3.2.3 Viscosity.** When determined in accordance with ASTM D 562, the viscosity of the tinting medium shall not be greater than 125 Kreh Units (K.U.).

**3.2.4 Flash point.** When tested in accordance with ASTM D 56, the flash point shall not be less than 60 °C (141 °F).

**Table I**

**Quantitative Requirements.**

Type	Prime pigment	Dry prime pigment content, percent by wt. min.	Percent total pigment by wt. min. <u>1/</u>	Percent solids, by wt. min. <u>2/</u>	Grind, Hegman, min. <u>3/</u>
1a	Carbon black or Lampblack	9.0	31	47	6.5
2a	Phthalocyanine blue	5.1	40	46	6.5
3a	Burnt Sienna <u>4/</u>	31	55	65	6.5
3b	Burnt Umber <u>4/</u>	31	48	57	6.5
3c	Raw Sienna <u>4/</u>	21	45	55	6.5
3d	Raw Umber	20	45	53	6.5
4b	Phthalocyanine green	6.2	42	54	6.5
5b	Hansa Orange <u>5/</u>	—	18	36	6.5
6a	Bright Red Iron Oxide	59	61	70	6.5
7b	Hansa Yellow.	12	42	49	6.5

1/ Test method ASTM D 2698 shall be used for referee testing.

2/ Test method ASTM D 2369 shall be used for referee testing.

3/ Test method ASTM D 1210 shall be used for referee testing.

4/ The prime pigment may be a combination of raw umber, iron oxides, and carbon black.

5/ The prime pigment also may be Dinitraniline Orange, PO 5, or Perinone Orange, PO 43.

**3.2.5 Compatibility.** The tinting medium shall mix easily with an oil based alkyd, a latex, and a rubber paint in a ratio a 1:50. After the resulting mixtures have stood for five minutes, they shall be applied to glass panels conforming to method 2021 of FED-STD-141 to a wet film thickness of 51 $\mu$ m (2 mils). While the panels are still wet, rub up an area using the index finger in a circular motion for a minimum of 20 revolutions. Exert light pressure of the finger while rubbing so as not to rub-off the film. Allow the paint to dry for 48 hours at room temperature. Then, visually examine the dried film. There shall be no color streaks, pigment flotation, or difference in color, gloss, or texture between the rubbed-up area and the unrubbed-up area. For referee purposes, the paints used shall meet the requirements of TT-E-489, TT-E-2784, and TT-P-95.

**3.2.6 Quantitative Requirements.** In addition to the above requirements, all concentrates shall meet the quantitative requirements given in table I.

**3.2.7 Tinting strength.** Tinting strength, if specified in the contract or purchase order (see 7.2), shall be equal to or darker than the standard specified by the contracting officer.

#### **4. REGULATORY REQUIREMENTS.**

**4.1 Recovered materials.** The offeror/contractor is encouraged to use recovered materials to the maximum extent practical, in accordance with paragraph 23.403 of the Federal Acquisition Regulation (FAR).

**4.2 ODSs.** The tinting concentrates shall not contain any substance listed in 40 CFR part 82, Protection of Stratospheric Ozone.

**4.3 MSDS.** The manufacturer shall comply with requirements set forth by the Hazardous Communication Standard 29 CFR 1910.1200 (d) through (g). All Material Safety Data Sheets (MSDS) submitted must comply with provisions of FED-STD-313.

#### **5. QUALITY ASSURANCE PROVISIONS.**

**5.1 Contractor quality assurance.** The contractor shall maintain substantiating evidence that the product offered meets the salient characteristics of this Commercial Item Description and that the product conforms to the producer's own drawings, specifications, standards, and quality assurance practices, and is the same product offered for sale in the commercial marketplace.

The contractor shall provide the required information in a tabulated format and with enough clarity so that the formulation of the tested product can be traced compared to the offered product(s). The contractor shall also provide a summary of performance data, consisting of test reports, substantiating that the product to be supplied under this CID meets the special and quantitative requirements in 3.1 through 3.2.7, and table I, and is the same product offered for sale in the commercial marketplace.

The government reserves the right to require proof of such conformance prior to first delivery and thereafter as may be otherwise provided under the provisions of the contract.

#### **6. PACKAGING.**

Preservation, Packing and Marking shall be as specified in the contract or order. In addition, each container shall be labeled with the pigment name and directions for use.

A-A-3108 A

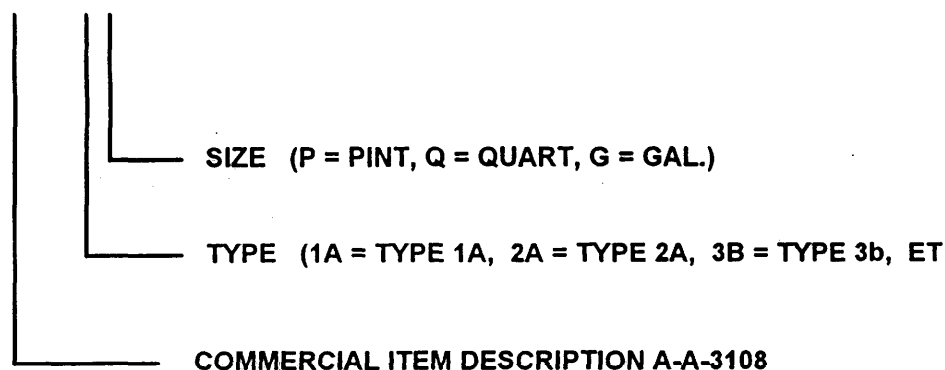
**7. NOTES.**

**7.1 Intended Use.** These dispersions and concentrates are intended for tinting both solvent and waterborne paints, enamels, and latexes. Except for Hansa Yellow, all may be used in exterior, as well as, interior paints. Hansa Yellow is only recommended for interior use.

**7.2 Ordering data.**

- (a) Title, number, and date of this specification.
- (b) Unit quantity required.
- (c) Packaging, packing, and marking requirements.
- (d) Color based upon pigmentation (see 2).
- (e) Tinting strength and Standard color, if specified (see 3.2.7).

**7.3 Part Identification Number (PIN).** The following part identification numbering procedure is for government purposes and does not constitute a requirement for the contractor.

**AA3108-1AP****7.4 Referenced documents.****Federal Standards:**

- FED-STD-141** - Paint, Varnish, Lacquer and Related Materials: Methods of Inspection, Sampling and Testing.
- FED-STD-313** - Material Safety Data, Transportation Data and Disposal Data for Hazardous Materials Furnished to Government Activities.

**Federal Specification:**

- TT-E-489** - Enamel, Alkyd, Gloss, Low VOC Content.
- TT-E-2784** - Enamel (Acrylic-Emulsion, Exterior).
- TT-P-95** - Paint, Rubber: For Swimming Pools and Other Concrete and Masonry Surfaces.

**National Toxicology Program:**

Annual Report on Carcinogens.

**ASTM Standards:**

- D 56 - Flash point by Tag Closed Tester.
- D 562 - Consistency of Paints Using the Stormer Viscometer.
- D 1210 - Fineness of Dispersion of Pigment-Vehicle Systems.
- D 1296 - Odor of Volatile Solvents and Diluents.
- D 1849 - Package Stability of Paint.
- D 2369 - Volatile Content of Coatings.
- D 2698 - Determination of the Pigment Content of Solvent-Reducible Paints by High-Speed Centrifuging

**7.5 Source of Documents.**

7.5.1 If there is a need to see paragraph 23.403 of the FAR, contact the contracting officer for a copy.

7.5.2 Copies of ASTM specifications and standards may be obtained from the American Society for Testing and Materials, 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959.

6.5.3 Copies of Federal Specifications and Standards may be obtained from the Federal Supply Service Bureau, Specification Section, Suite 8100, 470 East L'Enfant Plaza, SW, Washington, DC 20407.

7.5.4 Copies of the Annual Report on Carcinogens may be obtained from the National Toxicology Program, Annual Report on Carcinogens, PO Box 12233, Research Triangle Park, NC 27709.

**MILITARY INTERESTS:**

Custodian  
Navy - YD1

**Preparing Activity**

GSA-FSS

