

# AMPTIAC

ANC-5  
JUNE 1951

# Strength of Metal Aircraft Elements

01756

**DISTRIBUTION STATEMENT A**  
Approved for Public Release  
Distribution Unlimited



MUNITIONS BOARD  
AIRCRAFT COMMITTEE

Reproduced From  
Best Available Copy

20000907 178

**ANC-5**  
**JUNE 1951**

**AMENDMENT-1**  
**9 APRIL 1952**

## STRENGTH OF METAL AIRCRAFT ELEMENTS

- Page 15, Formula 1.6421 The square root sign should not extend over the  $D/t$ .
- Page 24, Table 2.111(b) The vertical line separating the specifications for Sheet, Plate, Tube, Bar, and Rod—4130 should be removed.
- Page 34, Figure 2.6111 Delete the last sentence of the note appearing in the upper right hand corner and substitute the following. "The curves are based on the results of combined load tests of bolts with nuts finger tight."
- Page 32, Table 2.6111 (a) The "AN-3" designation in the left hand column should be lowered one line.
- Pages 36, 89, 90, 91, and 123, Tables 2.6115, 3.6113(b), (c), (d), 4.6113 Add the following qualifying note. "The strength values listed were based on the results of laboratory tests conducted under optimum conditions and should be used with caution."
- Page 37, Table 2.6122 (b) In lieu of " $F_b$ , Figure 2.321 for  $F_{tu}=80,000$  p. s. i.," substitute the following. "0.9 of the values of  $F_b$  from Figure 2.321 for  $F_{tu}=90,000$  p. s. i."
- Page 39, Section 2.61261 In the second and third lines of the left hand column on page 39, delete the figure references to Figures 2.6127(a), (b), and (c) and substitute figures 2.61261(a), (b), and (c) in lieu thereof.
- Page 46, Table 3.111 (b) Delete specification AN-A-13 and substitute "QQ-A-362."
- Page 48, Table 3.111(d) Delete specification QQ-A-245 and substitute "QQ-A-255."
- Page 53, Table 3.111(i) Delete specification QQ-A-325 and substitute "QQ-A-270."
- Pages 57 and 58, Tables 3.112(a), (b), and (d) Add the following qualifying note: "Values given are applicable to forged, rolled, and extruded products."
- Pages 86 and 87, Tables 3.6112(a), (b), (c), and (d) On the "Clad Sheet Material" lines add 24S-T4 in addition to and wherever 24S-T3 is presently listed.
- Page 92, Table 3.6116 In the first column change " $\frac{3}{8}$ " to " $\frac{1}{2}$ ".
- Page 92, Table 3.6122 (a) In footnote one delete specification QQ-A-245 and substitute specification QQ-A-255.
- Page 94, Table 3.6122 (c) In the next to last horizontal and vertical columns delete specification QQ-A-245 and substitute specification QQ-A-255.
- Page 96, Table 4.111(a) In column 4, "Sheet, M-1, QQ-M-54, Hard Rolled," the value for  $F_{br}$  ( $e/D=1.5$ ) should be 33 instead of 55.
- Page 97, Table 4.111(b) Delete the alloy designations "M1A" from the fifteenth column and "AZ61A" from the sixteenth and seventeenth columns and substitute "AZ61A" and "AZ80A" respectively.

ANC-5 BULLETIN

# Strength of Metal Aircraft Elements

DEPARTMENT OF THE NAVY  
BUREAU OF AERONAUTICS

DEPARTMENT OF THE AIR FORCE  
AIR RESEARCH AND DEVELOPMENT COMMAND

DEPARTMENT OF COMMERCE  
CIVIL AERONAUTICS ADMINISTRATION

(Revised Edition June 1951)

ISSUED BY THE SUBCOMMITTEE ON AIR FORCE-NAVY-CIVIL AIRCRAFT DESIGN CRITERIA  
OF THE MUNITIONS BOARD AIRCRAFT COMMITTEE

The contents of this document shall not be reproduced in whole or in part  
without specific authorization of the Munitions Board Aircraft Committee

## NOTICE

The reader is hereby notified that this document is subject to revision and amendment when and where such revision or amendment is necessary to effect agreement with the latest approved information on aircraft design criteria. When using this document the reader should therefore make certain that it is the latest revision and that all issued amendments, if any, are included herein. When ordering this document from the Superintendent of Documents, United States Government Printing Office, a request for all revisions and amendments thereto should be made to insure receipt of a complete document.

Copies of this document and amendments thereto may be obtained from the Superintendent of Documents, United States Government Printing Office, Washington 25, D. C.

# CONTENTS

	Page
REFERENCES . . . . .	xiii
<b>CHAPTER 1. GENERAL</b>	
1.1 Purpose and Use of Document . . . . .	1
1.11 Introduction . . . . .	1
1.12 Scope of Document . . . . .	1
1.13 Use of Design Mechanical Properties . . . . .	1
1.2 Standard Structural Symbols . . . . .	1
1.3 Commonly Used Formulas . . . . .	3
1.31 General . . . . .	3
1.32 Simple Unit Stresses . . . . .	3
1.33 Combined Stresses . . . . .	3
1.34 Deflections (Axial) . . . . .	3
1.35 Deflections (Bending) . . . . .	3
1.36 Deflections (Torsion) . . . . .	3
1.37 Transverse Deformations . . . . .	3
1.38 Basic Column Formulas . . . . .	3
1.39 Basic Column Formulas (Nondimensional) . . . . .	4
1.4 Basic Principles and Definitions . . . . .	4
1.41 General . . . . .	4
1.42 Stress . . . . .	4
1.421 General . . . . .	4
1.422 Normal and Shear Stresses . . . . .	4
1.43 Strain . . . . .	4
1.431 Axial Strain . . . . .	4
1.432 Lateral Strain . . . . .	4
1.433 Shearing Strain . . . . .	4
1.44 Tensile Properties . . . . .	4
1.441 General . . . . .	4
Figure 1.441. Typical Tensile Stress-Strain Diagrams . . . . .	5
1.442 Modulus of Elasticity ( $E$ ) . . . . .	4
1.443 Tensile Proportional Limit ( $F_{tp}$ ) . . . . .	6
1.444 Tensile Yield Stress ( $F_{ty}$ ) . . . . .	6
1.445 Ultimate Tensile Stress ( $F_{tu}$ ) . . . . .	6
1.45 Compressive Properties . . . . .	6
1.451 General . . . . .	6
1.452 Ultimate Compressive Stress ( $F_{cu}$ ) . . . . .	6
1.46 Shear Properties . . . . .	7
1.461 General . . . . .	7
1.462 Modulus of Rigidity ( $G$ ) . . . . .	7
1.463 Proportional Limit in Shear ( $F_{sp}$ ) . . . . .	7
1.464 Yield and Ultimate Stresses in Shear . . . . .	7
1.47 Creep and Stress-Rupture Properties . . . . .	7
1.471 General . . . . .	7
Figure 1.471. Typical Creep Rupture Curve . . . . .	7
1.472 Total Creep . . . . .	8
1.473 Minimum Creep Rate . . . . .	8
1.474 Transition Point . . . . .	8
1.475 Rupture Stress . . . . .	8
1.48 Fatigue Properties . . . . .	8
1.481 General . . . . .	8
Figure 1.481. Typical Fatigue Loadings . . . . .	8
1.482 Stress . . . . .	8
1.4821 Maximum Stress . . . . .	8
1.4822 Minimum Stress . . . . .	8
1.4823 Mean Stress . . . . .	8

CHAPTER 1. GENERAL—Continued		Page
1.4824	Stress Range . . . . .	9
1.4825	Stress Amplitude . . . . .	9
1.5	Types of Failures . . . . .	9
1.51	General . . . . .	9
1.52	Material Failures . . . . .	9
1.521	General . . . . .	9
1.522	Direct Tension or Compression . . . . .	9
1.523	Shear . . . . .	9
1.524	Bearing . . . . .	9
1.525	Bending . . . . .	9
1.526	Failure due to Stress Concentrations . . . . .	9
1.527	Failure due to Fatigue . . . . .	9
1.528	Failure from Combined Stresses . . . . .	10
1.53	Instability Failures . . . . .	10
1.531	General . . . . .	10
1.532	Instability Failures Under Compressive Loadings . . . . .	10
1.533	Bending Instability Failures . . . . .	10
1.534	Torsional Instability Failures . . . . .	10
1.535	Failure under Combined Loadings . . . . .	11
	Figure 1.535. Typical Interaction Curves for Combined Loading Conditions . . . . .	12
1.6	Columns . . . . .	12
1.61	General . . . . .	12
1.62	Primary Instability Failure . . . . .	12
1.621	General . . . . .	12
1.622	Long Columns . . . . .	12
1.623	Short Columns . . . . .	13
1.624	Column Yield Stress ( $F_{co}$ ) . . . . .	13
1.63	Nondimensional Column Curves for Primary Failure . . . . .	13
1.631	General . . . . .	13
1.632	Typical Column Curves . . . . .	14
	Figure 1.632. Various Column Curves in Nondimensional Form . . . . .	14
1.64	Local Instability Failure . . . . .	14
1.641	General . . . . .	14
1.642	Crushing or Crippling Stress ( $F_{cc}$ ) . . . . .	15
1.65	Columns of Unconventional Cross Section . . . . .	15
1.651	General . . . . .	15
1.652	Nature of "Short Column" Curve . . . . .	15
1.653	Local Failure . . . . .	15
1.654	Reduction of Test Results on Aluminum and Magnesium Alloys to Standard . . . . .	15
	Figure 1.654 (a). Nondimensional Material Correction Chart for 24S-T3 Sheet . . . . .	16
	Figure 1.654 (b). Nondimensional Material Correction Chart for 24S-T3 Clad Sheet . . . . .	16
	Figure 1.654 (c). Nondimensional Material Correction Chart for 24S-T4 Extrusions less than ¼ inch thick . . . . .	17
	Figure 1.654 (d). Nondimensional Material Correction Chart for 24S-T4 Extrusions ¼ to 1½ inches thick . . . . .	17
	Figure 1.654 (e). Nondimensional Material Correction Chart for 24S-T3 Tubing . . . . .	18
	Figure 1.654 (f). Nondimensional Material Correction Chart for 14S-T3 (R301-T3) Clad Sheet . . . . .	18
	Figure 1.654 (g). Nondimensional Material Correction Chart for 75S-T6 Clad Sheet . . . . .	19
	Figure 1.654 (h). Nondimensional Material Correction Chart for M or AM3S Open Extrusions . . . . .	19
	Figure 1.654 (i). Nondimensional Material Correction Chart for FS-1, J-1, O-1, AM C52S, AM C57S or AM C58S Open Extrusions . . . . .	20
	Figure 1.654 (j). Nondimensional Material Correction Chart for AM-C58S-T5 or O-1HTA Open Extrusions . . . . .	20
	Figure 1.654 (k). Nondimensional Material Correction Chart for FS-1h or AM C52S-H Sheet . . . . .	21
1.655	Reduction of Test Results to Standard—Alternate Method . . . . .	21
	Figure 1.655. Illustrative Material Correction Curves for Columns (Alternate Method) . . . . .	22
1.7	Thin-Walled and Stiffened Thin-Walled Sections . . . . .	21
1.71	General . . . . .	21

## CHAPTER 2. STEEL

	Page	
2.1	General Properties . . . . .	23
2.11	Normal (Room) Temperature Properties . . . . .	23
2.111	Design Mechanical Properties . . . . .	23
	Table 2.111 (a). Design Mechanical Properties of Plain Carbon Steels . . . . .	23
	Table 2.111 (b). Design Mechanical Properties of Alloy Steels . . . . .	24
	Table 2.111 (c). Design Mechanical Properties of Corrosion Resisting and Heat Treated Corrosion Resisting Steels . . . . .	25
2.112	Fatigue Properties . . . . .	25
	Table 2.112 (a). Rotating Beam Fatigue Data for Ferrous Materials . . . . .	26
	Table 2.112 (b). Reversed Bending Fatigue Data for Chromium 18 percent, Nickel 8 percent Sheet Steel, Longitudinal Direction . . . . .	26
2.113	Typical Stress-Strain and Tangent Modulus Data . . . . .	26
	Figure 2.113 (a) through (d). Tangent Modulus Curves Derived from Stress-Strain Curves for Corrosion Resisting (Stainless) Steel Sheet and Plate . . . . .	27
2.12	Temperature Effects . . . . .	26
2.13	Criteria for Design Mechanical Material Properties . . . . .	26
2.2	Columns . . . . .	26
2.21	Primary Failure . . . . .	26
	Table 2.21. Column Formulas for Round Steel Tubes . . . . .	28
2.22	Local Failure . . . . .	26
2.221	Effects of Welding . . . . .	26
2.23	Column Stress Curves . . . . .	26
	Figure 2.23 (a). Allowable Column Stress for 1025 Steel Round Tubing . . . . .	28
	Figure 2.23 (b). Allowable Column and Crushing Stresses for Chrome Molybdenum Streamline Tubing $F_{ty}=75,000$ p. s. i. . . . .	28
	Figure 2.23 (c). Allowable Column Stress for Heat-Treated Alloy Steel Round Tubing . . . . .	29
2.24	Column Load Curves . . . . .	29
2.3	Beams . . . . .	29
2.31	General . . . . .	29
2.32	Simple Beams . . . . .	29
2.321	Round Tubes . . . . .	29
	Figure 2.321. Bending Modulus of Rupture Chrome Molybdenum Steel Tubing . . . . .	30
2.322	Unconventional Cross Sections . . . . .	29
2.33	Built-up Beams . . . . .	29
2.34	Thin-Web Beams . . . . .	29
2.4	Torsion . . . . .	29
2.41	General . . . . .	29
2.42	Allowable Torsional Shear Stresses . . . . .	29
	Figure 2.42 (a). Torsional Modulus of Rupture of 1025 Steel Round Tubing . . . . .	31
	Figure 2.42 (b). Torsional Modulus of Rupture of Round Alloy Steel Tubing . . . . .	31
2.5	Combined Loadings . . . . .	32
2.51	Round Tubes in Bending and Compression . . . . .	32
2.52	Tubes in Bending and Torsion . . . . .	32
2.53	Tubes in Bending, Compression, and Torsion . . . . .	32
2.6	Joints, Parts, and Fittings . . . . .	33
2.61	Joints . . . . .	33
2.611	Riveted and Bolted Joints . . . . .	33
2.6111	Allowable Shear and Tensile Strengths for Bolts and Pins . . . . .	33
	Table 2.6111 (a). Shear and Tensile Strengths, Areas, and Moments of Inertia of Steel Bolts and Pins . . . . .	32
	Table 2.6111 (b). Shear and Tension Strengths of Internal Wrenching Bolts . . . . .	33
	Figure 2.6111. Combined Shear and Tension on AN-Steel Bolts . . . . .	34
2.6112	Allowable Bearing Stresses . . . . .	33
2.61121	Joints Having no Motion . . . . .	33
	Table 2.61121. Unit Bearing Strengths of Sheets on Bolts and Pins . . . . .	33
2.61122	Joints Having Motion . . . . .	35
	Table 2.61122 (a). Bearing Factors for Plain Bearings Having no or Infrequent Relative Rotation Under Design Loads . . . . .	35
	Table 2.61122 (b). Ultimate Bearing Stress for Plain Lubricated Bearings Having Frequent Relative Motion . . . . .	35
2.6113	Hollow-End Rivets . . . . .	35

CHAPTER 2. STEEL—Continued		Page
2.6114	High Shear Rivets . . . . .	35
	Table 2.6114. Allowable Single Shear Strengths 18-8 Corrosion Resistant Steel Rivets . . . . .	35
2.6115	Blind Rivets . . . . .	35
	Table 2.6115. Ultimate and Yield Strengths for Blind Monel Cherry Rivets in Corrosion Resistant Sheet . . . . .	36
2.6116	Lockbolts . . . . .	36
2.612	Welded Joints . . . . .	36
2.6121	Fusion Welds—Arc and Gas . . . . .	36
2.6122	Effect on Adjacent Parent Metal when Fusion (arc or gas) Processes are Employed . . . . .	37
	Table 2.6122 (a). Allowable Ultimate Tensile Stresses Near Fusion Welds in 4130, 4140, 4340, or 8630 Steels . . . . .	37
	Table 2.6122 (b). Allowable Bending Modulus of Rupture Near Fusion Welds in 4130, 4140, 4340, or 8630 Steels . . . . .	37
2.6123	Allowable Strength-Weld Metal . . . . .	37
	Table 2.6123. Weld Metal Joint Strengths . . . . .	37
2.6124	Welded Cluster . . . . .	37
2.6125	Flash Welds . . . . .	37
	Table 2.6125 (a). Allowable Ultimate Tensile Stresses for Flash Welds in Steel Tubing . . . . .	38
	Table 2.6125 (b). Allowable Bending Modulus of Rupture for Flash Welds in Steel Tubing . . . . .	38
2.6126	Spot Welding . . . . .	37
	Table 2.6126 (a). Spotweld Maximum Design Shear Strength Standards for Uncoated Steels and Nickel Alloys . . . . .	38
	Table 2.6126 (b). Minimum Edge Distances for Spotwelded Joints . . . . .	38
2.61261	Reduction in Tensile Strength of Parent Metal Due to Spotwelding . . . . .	38
	Figure 2.61261 (a). Efficiency of the Parent Metal in Tension for Spotwelded 302-1A, 347-1A, and 302 $\frac{1}{2}$ H Corrosion Resisting Steels . . . . .	39
	Figure 2.61261 (b). Efficiency of the Parent Metal in Tension for Spotwelded 302 $\frac{1}{2}$ H Corrosion Resisting Steel . . . . .	40
	Figure 2.61261 (c). Efficiency of the Parent Metal in Tension for Spotwelded 302-H Corrosion Resisting Steel . . . . .	40
2.613	Brazed Joints of Steel and High Melting Point, Non-Ferrous Alloys . . . . .	39
2.6131	Copper Brazing . . . . .	39
2.6132	Silver Brazing . . . . .	39
2.614	Adhesive Bonded Joints . . . . .	41
2.62	Parts . . . . .	41
2.621	Antifriction Bearings . . . . .	41
2.622	Antifriction Bearing Control Pulleys . . . . .	41
	Table 2.622. Static Yield Strengths for Control Pulleys . . . . .	41
2.623	Cable and Cable Connections . . . . .	41
2.6231	Cable Connections . . . . .	41
2.6232	Strength and Load-Deformation Data for Aircraft Cable . . . . .	41
	Table 2.6232. Strength of Steel Cable . . . . .	42
	Figure 2.6232. Load-Deformation Data for Steel Cable . . . . .	43
CHAPTER 3. ALUMINUM ALLOYS		
3.1	General Properties . . . . .	44
3.11	Normal (Room) Temperature Properties . . . . .	44
3.111	Design Mechanical Properties . . . . .	44
	Table 3.111 (a). Design Mechanical Properties of Bare 24S Sheet and Plate . . . . .	45
	Table 3.111 (b). Design Mechanical Properties of Clad 24S Sheet and Plate . . . . .	46
	Table 3.111 (c). Design Mechanical Properties of Clad 24S Sheet . . . . .	47
	Table 3.111 (d). Design Mechanical Properties of Clad 14S and R301 Sheet and Plate . . . . .	48
	Table 3.111 (e). Design Mechanical Properties of 75S Sheet and Plate . . . . .	49
	Table 3.111 (f). Design Mechanical Properties of 52S and 61S Sheet . . . . .	50
	Table 3.111 (g). Design Mechanical Properties of Aluminum Alloy Rolled Bar and Rod, Tubing, and Shapes . . . . .	51
	Table 3.111 (h). Design Mechanical Properties of 14S and 75S Extruded Bar, Rod, and Shapes . . . . .	52
	Table 3.111 (i). Design Mechanical Properties of 24S and 61S Extruded Shapes . . . . .	53
	Table 3.111 (j). Design Mechanical Properties of 14S and 75S Hand Forged Stock . . . . .	54
	Table 3.111 (k). Design Mechanical Properties of Aluminum Alloy Die Forgings . . . . .	55
	Table 3.111 (l). Design Mechanical Properties of Aluminum Alloy Castings . . . . .	56
	Table 3.111 (m). Design Mechanical Properties of Heat Treated Cold Worked and Aged 24S Alloy Extrusions and Tubing . . . . .	57



CHAPTER 3. ALUMINUM ALLOYS—Continued		Page
3.112	Fatigue Properties . . . . .	56
	Table 3.112 (a). Average Fatigue Strengths of Smooth Machined Round Specimens Under Completely Reversed Flexure . . . . .	57
	Table 3.112 (b). Average Fatigue Strengths of Sharply Notched Round Specimens Under Completely Reversed Flexure . . . . .	57
	Table 3.112 (c). Average Fatigue Strengths of Flat Sheet Specimens Under Completely Reversed Flexure . . . . .	57
	Table 3.112 (d). Average Fatigue Strengths of Smooth Machined Round Specimens Under Repeated Axial Load . . . . .	58
3.113	Typical Stress-Strain and Tangent Modulus Data . . . . .	58
	Figure 3.113 (a). Typical Stress-Strain and Tangent Modulus Curves for Various Aluminum Alloy Sheet Materials . . . . .	59
	Figure 3.113 (b). Typical Stress-Strain and Tangent Compression Modulus Curves for 14S Aluminum Alloy Sheet . . . . .	60
	Figure 3.113 (c). Typical Stress-Strain and Tangent Modulus Curves for 24S and 14S Aluminum Alloy Extrusions . . . . .	61
	Figure 3.113 (d). Typical Stress-Strain and Tangent Modulus Curves for 61S and 75S Aluminum Alloy Extrusions . . . . .	62
	Figure 3.113 (e). Typical Stress-Strain and Tangent Modulus Curves for 14S-T6, 24S-T4, and 75S-T6 Aluminum Alloy Rolled Bar, Rod and Shapes . . . . .	63
3.12	Temperature Effects . . . . .	58
3.121	Low Temperature . . . . .	58
3.1211	Static Properties . . . . .	58
	Table 3.1211 (a). Acceptable Approximations of Effects of Low Temperatures on the Static Design Properties of Aluminum Alloys . . . . .	64
	Table 3.1211 (b). Effect of Various Temperatures on the Modulus of Elasticity of Aluminum Alloys . . . . .	64
3.1212	Fatigue Properties . . . . .	58
	Table 3.1212. Flexure Type Fatigue Data . . . . .	64
3.122	Elevated Temperature . . . . .	64
3.1221	General . . . . .	64
	Figure 3.1221 (a). Aluminum Alloy Tensile Properties at Elevated Temperatures . . . . .	65
	Figure 3.1221 (b). Aluminum Alloy Tensile Properties at Elevated Temperatures . . . . .	66
	Figure 3.1221 (c). Aluminum Alloy Tensile Properties at Elevated Temperatures . . . . .	67
	Figure 3.1221 (d). Elevated Temperature Properties of Wrought 24S-T3 Aluminum Alloy at 211° F . . . . .	68
	Figure 3.1221 (e). Elevated Temperature Properties of Wrought 24S-T3 Aluminum Alloy at 300° F . . . . .	69
	Figure 3.1221 (f). Elevated Temperature Properties of Wrought 24S-T3 Aluminum Alloy at 375° F . . . . .	70
	Figure 3.1221 (g). Elevated Temperature Properties of Wrought 75S-T6 Aluminum Alloy at 94° F . . . . .	71
	Figure 3.1221 (h). Elevated Temperature Properties of Wrought 75S-T6 Aluminum Alloy at 211° F . . . . .	72
	Figure 3.1221 (i). Elevated Temperature Properties of Wrought 75S-T6 Aluminum Alloy at 300° F . . . . .	73
	Figure 3.1221 (j). Elevated Temperature Properties of Wrought 75S-T6 Aluminum Alloy at 375° F . . . . .	74
	Figure 3.1221 (k). Elevated Temperature Properties of Clad 24S-T86 Aluminum Alloy (Heat Treated, Cold Worked, and Aged) at 211° F . . . . .	75
	Figure 3.1221 (l). Elevated Temperature Properties of Clad 24S-T86 Aluminum Alloy (Heat Treated, Cold Worked, and Aged) at 300° F . . . . .	76
	Figure 3.1221 (m). Elevated Temperature Properties of Clad 24S-T86 Aluminum Alloy (Heat Treated, Cold Worked and Aged) at 375° F . . . . .	77
3.1222	Static Properties . . . . .	78
3.1223	Creep and Stress Rupture Properties . . . . .	78
3.1224	Fatigue Properties . . . . .	78
	Table 3.1224. Cantilever-Beam Fatigue Strengths of Wrought Aluminum Alloys at Elevated Temperatures . . . . .	78
3.13	Criteria for Design Mechanical Properties . . . . .	79
3.131	Shear Strengths . . . . .	79
3.132	Tensile Strengths . . . . .	79
3.133	Bearing Strengths . . . . .	79

CHAPTER 3 ALUMINUM ALLOYS—Continued		Page
3.14	Rate of Stressing Effects . . . . .	79
3.2	Columns . . . . .	79
3.21	Primary Failure . . . . .	79
	Table 3.21. Column Formulas for Aluminum Alloy Tubing and/or Shapes . . . . .	79
3.22	Local Failure . . . . .	80
3.23	Column Stress Curves . . . . .	80
	Figure 3.23. Allowable Column and Crushing Stresses 24S and 61S Aluminum Alloy Tubing. . . . .	80
3.3	Beams . . . . .	80
3.31	General . . . . .	80
3.32	Simple beams . . . . .	80
3.321	Round Tubes . . . . .	80
	Figure 3.321. Bending Modulus of Rupture Aluminum Alloy Round Tubing Restrained Against Local Buckling at Loading Points . . . . .	80
3.322	Unconventional Cross-Sections . . . . .	81
3.33	Built-Up Beams . . . . .	81
3.34	Thin Web Beams . . . . .	81
3.4	Torsion . . . . .	81
3.41	General. . . . .	81
3.42	Allowable Torsional Shear Stresses . . . . .	81
	Figure 3.42. Torsional Modulus of Rupture-Aluminum Alloy Round Tubing . . . . .	81
3.5	Combined Loadings . . . . .	81
3.51	Round Tubes in Bending and Compression . . . . .	81
3.52	Tubes in Bending and Torsion. . . . .	82
3.53	Tubes in Bending, Compression, and Torsion . . . . .	82
3.6	Joints, Fittings, and Parts . . . . .	82
3.61	Joints . . . . .	82
3.611	Riveted and Bolted Joints . . . . .	82
3.6111	Protruding Head Rivets and Bolts . . . . .	82
	Table 3.6111 (a). Shear Strength of Protruding and Flush Head Aluminum Alloy Rivets . . . . .	83
	Table 3.6111 (b). Aluminum Alloy Sheet and Plate—Bearing Factors . . . . .	84
	Table 3.6111 (c). Design Mechanical Properties for Aluminum Alloy Rivets . . . . .	85
	Table 3.6111 (d). Unit Bearing Strength of Sheet on Rivets $F_{br}=100,000$ p. s. i . . . . .	85
3.6112	Flush Rivets . . . . .	85
	Table 3.6112 (a). Ultimate Strength of Solid 100° Machine Countersunk Rivets . . . . .	86
	Table 3.6112 (b). Yield Strength of Solid 100° Machine Countersunk Rivets . . . . .	86
	Table 3.6112 (c). Ultimate Strength of Solid 100° Dimpled Rivets . . . . .	87
	Table 3.6112 (d). Yield Strength of Solid 100° Dimpled Rivets . . . . .	87
3.6113	Blind Rivets . . . . .	88
	Table 3.6113 (a). Rivet Shear Strengths for Blind Rivets (Protruding and Flush Heads) . . . . .	88
	Table 3.6113 (b). Ultimate and Yield Strengths for Protruding Head Blind Rivets . . . . .	89
	Table 3.6113 (c). Ultimate and Yield Strengths for 100° Double Dimpled Blind Rivets . . . . .	90
	Table 3.6113 (d). Ultimate and Yield Strengths for 100° Machine Countersunk Blind Rivets . . . . .	91
3.6114	Hollow-End Rivets . . . . .	92
3.6115	High Shear Rivets. . . . .	92
3.6116	Lockbolt and Lockbolt Stumps . . . . .	92
	Table 3.6116. Ultimate Single Shear and Tensile Strengths of Protruding and Flush Head Lockbolts. . . . .	92
3.612	Welded Joints . . . . .	92
3.6121	Fusion Welds . . . . .	92
3.6122	Spot Welding . . . . .	92
	Table 3.6122 (a). Spotweld Maximum Design Shear Strength Standards for Bare and Clad Aluminum Alloys. . . . .	92
	Table 3.6122 (b). Minimum Edge Distances for Spotwelded Joints . . . . .	93
	Table 3.6122 (c). Acceptable Aluminum and Aluminum Alloy Combinations for Spotwelding. . . . .	94
3.61221	Reduction in Tensile Strength of Parent Metal Due to Spotwelding . . . . .	92
	Figure 3.61221. Efficiency of the Parent Metal in Tension for Spotwelded Aluminum Alloys . . . . .	93
3.6123	Aluminum Brazing. . . . .	93
3.613	Adhesive Bonded Joints . . . . .	93

	Page
CHAPTER 4. MAGNESIUM ALLOYS	
4.1 General Properties . . . . .	95
4.11 Normal (Room) Temperature Properties . . . . .	95
4.111 Design Mechanical Properties . . . . .	95
Table 4.111 (a). Design Mechanical Properties of Magnesium Alloy Sheet, Tubes, and Shapes . . . . .	96
Table 4.111 (b). Design Mechanical Properties of Magnesium Alloy Bars and Rods, Sand Castings, and Forgings . . . . .	97
4.112 Fatigue Properties . . . . .	95
Table 4.112 (a). Rotating-Beam Fatigue Strength . . . . .	98
Table 4.112 (b). Repeated-Flexure Fatigue Strength . . . . .	99
Table 4.112 (c). Direct Tension-Compression Fatigue Strength . . . . .	100
4.113 Typical Stress-Strain and Tangent Modulus Data . . . . .	101
Figure 4.113 (a). Typical Stress-Strain and Tangent Modulus Curves for Magnesium Alloy Sheet and Extruded Shapes . . . . .	101
Figure 4.113 (b). Typical Stress-Strain and Tangent Modulus Curves for Magnesium Alloy Sand Castings . . . . .	102
4.12 Temperature Effects . . . . .	103
4.121 Low Temperature . . . . .	103
4.122 Elevated Temperature . . . . .	103
4.1221 Static Properties . . . . .	103
Figure 4.1221 (a). Elevated Temperature Properties of Forged M (annealed 1 hour at 700° F.) Magnesium Alloy at 200° F. (Tensile) (R. T. $F_{tu}$ =33,500 p. s. i.) . . . . .	104
Figure 4.1221 (b). Elevated Temperature Properties of Forged M (annealed 1 hour at 700° F.) Magnesium Alloy at 300° F. (Tensile) (R. T. $F_{tu}$ =33,500 p. s. i.) . . . . .	105
Figure 4.1221 (c). Elevated Temperature Properties of Forged M (annealed 1 hour at 700° F.) Magnesium Alloy at 400° F. (Tensile) (R. T. $F_{tu}$ =33,500 p. s. i.) . . . . .	106
Figure 4.1221 (d). Elevated Temperature Properties of Forged O-1HTA and AMC 58S-T51 Magnesium Alloy at 200° F. (Tensile) (R. T. $F_{tu}$ =49,000 p. s. i.) . . . . .	107
Figure 4.1221 (e). Elevated Temperature Properties of Forged O-1HTA and AMC 58S-T51 Magnesium Alloy at 300° F. (Tensile) (R. T. $F_{tu}$ =49,000 p. s. i.) . . . . .	108
Figure 4.1221 (f). Elevated Temperature Properties of Forged O-1HTA and AMC 58S-T51 Magnesium Alloy at 400° F. (Tensile) (R. T. $F_{tu}$ =49,000 p. s. i.) . . . . .	109
Figure 4.1221 (g). Elevated Temperature Properties of Forged EM51-HTA Magnesium Alloy at 300° F. (Tensile) (R. T. $F_{tu}$ =37,000 p. s. i.) . . . . .	110
Figure 4.1221 (h). Elevated Temperature Properties of Forged EM51-HTA Magnesium Alloy at 400° F. (Tensile) (R. T. $F_{tu}$ =37,000 p. s. i.) . . . . .	111
Figure 4.1221 (i). Elevated Temperature Properties of Forged EM51-HTA Magnesium Alloy at 500° F. (Tensile) (R. T. $F_{tu}$ =37,000 p. s. i.) . . . . .	112
Figure 4.1221 (j). Elevated Temperature Properties of EM51-HTA Magnesium Alloy at 600° F. (Tensile) (R. T. $F_{tu}$ =37,000 p. s. i.) . . . . .	113
Figure 4.1221 (k). Elevated Temperature Properties of Sand Cast Dowmetal H or Mazlo AM265 Magnesium Alloy (Heat Treated and Stabilized) at 200° F. (Tensile and Fatigue) . . . . .	114
Figure 4.1221 (l). Elevated Temperature Properties of Sand Cast Dowmetal H or Mazlo AM265 Magnesium Alloy (Heat Treated and Stabilized) at 300° F. (Tensile and Fatigue) . . . . .	115
Figure 4.1221 (m). Elevated Temperature Properties of Sand Cast Dowmetal H or Mazlo AM265 Magnesium Alloy (Heat Treated and Stabilized) at 400° F. (Tensile) . . . . .	116
4.1222 Fatigue Properties . . . . .	117
4.1223 Creep and Stress Rupture Properties . . . . .	117
4.13 Criteria for Design Mechanical Properties . . . . .	117
4.131 Shear Strengths . . . . .	117
4.132 Tensile Strengths . . . . .	117
4.133 Bearing Strengths . . . . .	117
4.2 Columns . . . . .	117
4.21 Primary Failure . . . . .	117
Table 4.21 (a). Column Formulas for Magnesium Alloy Extruded Open Shapes . . . . .	117
Table 4.21 (b). Column Formula for FS-1h Magnesium Alloy Sheet . . . . .	120
4.22 Local Failure . . . . .	120
4.23 Column Stress Curves . . . . .	120
Figure 4.23 (a). Allowable Column Stresses for Magnesium Alloy Columns . . . . .	118
Figure 4.23 (b). Allowable Column Stresses for FS-1h Magnesium Alloy Sheet . . . . .	119

CHAPTER 4. MAGNESIUM ALLOYS—Continued		Page
4.3	Beams . . . . .	120
4.31	General . . . . .	120
4.32	Simple Beams . . . . .	120
4.321	Round Tubes . . . . .	120
	Figure 4.321. Bending Modulus of Rupture of Magnesium Alloy Round Tubing . . . . .	120
4.4	Torsion . . . . .	121
4.41	General . . . . .	121
4.42	Allowable Torsion Shear Stresses . . . . .	121
	Figure 4.42. Torsional Modulus of Rupture for Magnesium Alloy Round Tubing . . . . .	121
4.5	Combined Loadings . . . . .	121
4.6	Joints, Fittings, and Parts . . . . .	121
4.61	Joints . . . . .	121
4.611	Riveted and Bolted Joints . . . . .	121
4.6111	Protruding Head Rivets . . . . .	121
4.6112	Flush Rivets . . . . .	122
4.6113	Blind Rivets . . . . .	122
	Table 4.6113. Ultimate and Yield Strengths for Blind 56S Aluminum Cherry Rivets in Magnesium Sheet . . . . .	123
4.612	Welded Joints . . . . .	124
4.6121	Fusion Welds . . . . .	124
4.6122	Spot Welding . . . . .	124
	Table 4.6122 (a). Spotweld Maximum Design Shear Strength Standards for Magnesium Alloys . . . . .	124
	Table 4.6122 (b). Minimum Edge Distances for Spotweld Joint . . . . .	124
4.613	Adhesive Bonded Joints . . . . .	124
CHAPTER 5. MISCELLANEOUS METALS		
5.1	General Properties . . . . .	125
5.11	Normal (Room) Temperature Properties . . . . .	125
5.111	Design Mechanical Properties . . . . .	125
	Table 5.111. Design Mechanical Properties—Castings . . . . .	125

## REFERENCES

- 1.41 Timoshenko, *Theory of Elastic Stability*. McGraw-Hill, 1936.
- 1.441 Federal Specification No. QQ-M-151a, *Metals: General Specification for Inspection of*. Amendment—3, March 28, 1945.
- 1.451 NACA Technical Report No. 649, *The Pack Method for Compressive Tests of Thin Specimens of Materials Used in Thin-Wall Structures*. Aitchison and Tuckerman, 1939.
- 1.471 (a) *Study of the Forming Properties of Aluminum Alloy Sheet at Elevated Temperatures*. OPRD Project.  
 (1) Part X, *Tensile Properties at Elevated Temperatures after Prolonged Times at Temperature*. OPRD W-146. 1945.  
 (2) Part XI, *Bearing Properties of 24S-T Sheet and Shear Strength of 24S-T Rivets at Elevated Temperatures after Prolonged Heating*. OPRD-W-165. 1944.  
 (3) Part XII, *Stress Rupture and Creep Tests in Tension at Elevated Temperatures*. OPRD-W-216. 1945.
- 1.471 (b) *Compressive Properties at Elevated Temperatures after Prolonged Heating* (Flanigan, Tedsen and Dorn). Proc. ASTM 1946, Vol. 46, pp. 951-970.
- 1.471 (c) *High Temperature Properties of Light Alloys (NA-137): Part I—Aluminum* (Wyman). OSRD Report M-251. 1944.
- 1.471 (d) *High Temperature Properties of Light Alloys (NA-137): Part II—Magnesium* (Wyman). OSRD Report M-292. 1944.
- 1.471 (e) *Tensile and Creep Strengths of Some Magnesium Base Alloys at Elevated Temperatures* (Moore and McDonald). Proc. ASTM 1946, Vol. 46, pp. 970-990.
- 1.475 *Compressive Properties at Elevated Temperatures after Prolonged Heating* (Flanigan, Tedsen and Dorn). Proc. ASTM 1946, Vol. 46, pp. 951-970.
- 1.526 *Corrugated Panels Under Combined Compression and Shear Load* (Sanderson and Fischel). Journal of Aeronautical Sciences, February 1940.
- 1.527 (a) Jackson, L. R., Grover, H. J., McMaster, R. C., *Survey of Available Information on the Behavior of Aircraft Materials and Structures Under Repeated Load*. War Metallurgy Committee Survey Project SPX27. 31 December 1945 (Battelle Memorial Institute).
- 1.527 (b) Jackson, L. R., Grover, H. J., and McMaster, R. C., Battelle Memorial Institute, *Advisory Report of Fatigue Properties of Aircraft Materials and Structures*. OSRD No. 6600, Serial No. M-653.
- 1.534 *The Stability of Thin-Walled Tubes Under Torsion*. NACA TN No. 479.
- 1.624 Aluminum Research Laboratories Technical Paper No. 1, *Column Strength of Various Aluminum Alloys*.
- 1.64 (a) *Local Instability of Centrally Loaded Columns of Channel Section and Z-Section* (Lundquist). NACA TN 722.
- 1.64 (b) *Local Instability of I, Z, Channel, and Rectangular Tube Sections* (Stowell and Lundquist). NACA TN 743.
- 1.71 NACA Index No. 7E29, *Index of Aircraft Structures Research Reports*, June 1947.
- 2.24 *Aircraft Tubing Data*. Summerill Tubing Co., Bridgeport, Montg. County, Pennsylvania.
- 2.42 National Bureau of Standards Report, *Revision of Fig. 4-22, ANC-5, Torsional Modulus of Rupture of Round Alloy Steel Tubing*. NBS No. 6531-103.
- 2.5 Navy Dept. Bureau of Aeronautics Structures Memo No. 12, *Strength of Heat-Treated Chromium—Molybdenum—Steel Tubing Under Combined Loading*.
- 2.53 *Strength of Tubing Under Combined Axial and Transverse Loading* (Tuckerman, Petrenko, and Johnson). NACA TN 307.
- 2.614 ANC-23. "Sandwich Construction for Aircraft," Parts I and II.
- 2.62 *Strength of Welded Aircraft Joints* (Bruggeman). NACA Report No. 584.
- 3.1 *The Elastic Constants for Wrought Aluminum Alloy*. NACA TN 966.
- 3.11 (a) *Factors Influencing the Fatigue Strength of Materials*. NACA TN No. 987.
- 3.11 (b) Mosely, D. L., *Notch Effects in High Strength Aluminum Alloy Spar Caps*. J. Aero. Sci., Vol. 13, 1946, p. 397.
- 3.11 (c) Schapiro, L., and North, H. E., *Notch Sensitivity of High Strength Aluminum Alloys, Theoretical Aspects*. J. Aero. Sci., Vol. 13, 1946, p. 391.
- 3.11 (d) Schapiro, L., and Esling, R. H., *Stress Notch Sensitivity With Eccentric Holes*. Trans. A. S. M. E., Vol. 70, 1948, p. 135.
- 3.11 (e) Stevenson, C. H., *The Effects of Open Holes on the Tensile Strength of Some Aluminum Alloys*. J. Aero. Sci., Vol. 13, 1946, p. 395.
- 3.111 (a) Mosely, D. L., *Notch Effects in High Strength Aluminum Alloy Spar Caps*. J. Aero. Sci., Vol. 13, 1946, p. 397.
- 3.111 (b) Schapiro, L., and North, H. E., *Notch Sensitivity of High Strength Aluminum Alloys, Theoretical Aspects*. J. Aero. Sci., Vol. 13, 1946, p. 391.
- 3.111 (c) Schapiro, L., and Esling, R. H., *Stress Notch Sensitivity With Eccentric Holes*. Trans. A. S. M. E., Vol. 70, 1948, p. 135.

- 3.111 (d) Stevenson, C. H., *The Effects of Open Holes on the Tensile Strength of Some Aluminum Alloys*. J. Aero. Sci., Vol. 13, 1946, p. 395.
- 3.112 (a) *Effect of Grain Direction on Fatigue Properties of Aluminum Alloys*. Project Engineering, July 1950.
- 3.112 (b) *How to Use High-Strength Aluminum Alloy*. Aviation Week, October 10, 1949.
- 3.112 (c) *Static and Fatigue Strength of High-Strength Aluminum-Alloy Bolted Joints*. NACA TN No. 2276, February 1951.
- 3.112 (d) *Results of Shear Fatigue Tests of Joints with  $\frac{3}{16}$ -inch Diameter 24S-T31 Rivets in 0.064 inch Thick Alclad Sheet*. NACA TN No. 2012.
- 3.1211 NACA TN No. 843, *A Summary of Results of Various Investigations of the Mechanical Properties of Aluminum Alloys At Low Temperatures*. By E. C. Hartman and W. H. Sharp.
- 3.1222 (a) *Compressive Properties of Aluminum Alloy Sheet at Elevated Temperatures* (Flanigan, Tedsen and Dorn). Proc. ASTM, 1946, Vol. 46, pp. 951-970.
- 3.1222 (b) Part XI: *Bearing Properties of 24S-T Sheet and Shear Strength of 24S-T Rivets at Elevated Temperatures after Prolonged Heating*. OPRD-W-165. 1944.
- 3.1223 Part XII: *Stress Rupture and Creep Tests in Tension at Elevated Temperatures*. OPRD-W-216. 1945.
- 3.1224 *High Temperature Properties of Light Alloys (NA-137): Part I, Aluminum* (Wyman). OSRD Report M-251. 1944.
- 3.133 (a) NACA TN No. 901, dated August 1943, *Bearing Strengths of Some Wrought-Aluminum Alloys*.
- 3.133 (b) NACA TN No. 920, dated December 1943, *Bearing Strengths of Bare and Alclad XA 75S-T and 24S-T 81 Aluminum Alloy Sheet*.
- 3.133 (c) NACA TN No. 974, dated February 1945, *Bearing Strengths of 75S-T Aluminum Sheet and Extruded Angle*.
- 3.133 (d) NACA TN No. 981, dated June 1945, *Bearing Strengths of 24S-T Aluminum Alloy Plate*.
- 3.133 (e) NACA TN No. 1172, dated March 1947, *Comparative Tests on Extruded 14S-T and Extruded 24S-T Hat-Shape Stiffener Sections*.
- 3.611 NACA TN No. 942 (Restricted), dated July 1944, *The Shear Strength of Aluminum Alloy Driven Rivets as Affected by Increasing D/t Ratios*.
- 3.6112 *Report on Flush Riveted Joint Strength*. ARC Rivet and Screw Allowables Sub-committee (Airworthiness Project 12), Revised May 25, 1948.
- 4.111 (a) Meriam, J. L., and Dorn, John E., *Properties and Heat Treatment of Magnesium Alloys: Part II, Notch Sensitivity of Magnesium Alloys*. OSRD No. 1819.
- 4.111 (b) Dorn, John E., and others, *Properties and Heat Treatment of Magnesium Alloys: Part V, Section I, The Sensitivity of Magnesium Alloy Sheet to Drilled, Reamed, and Punched Holes; Part V, Section II, The Notch Sensitivity of Magnesium Alloy Extrusions and the Influence of Various Factors*. OSRD No. 3043, Final Report, December 1943 (NRC Research Project NRC-21).
- 4.111 (c) Doan, J. P., and McDonald, J. C., *The Notch Sensitivity in Static and Impact Loading of Some Magnesium Base Alloys*. Proceedings, A. S. T. M., Vol. 46, 1946.
- 4.112 Found, George H., *The Notch Sensitivity in Fatigue Loading of Some Magnesium-Base and Aluminum-Base Alloys*. Proceedings ASTM, 1946.
- 4.12 (a) *Tensile and Creep Strengths of Some Magnesium-Base Alloys at Elevated Temperatures* (Moore and McDonald). Proc. ASTM, 1946, Vol. 46, pp. 970-990.
- 4.12 (b) McDonald, John C., *Tensile, Creep and Fatigue Properties of some Magnesium-Base Alloys*. Proceedings A. S. T. M., 1948.
- 4.122 *High Temperature Properties of Light Alloys (NA-137): Part II, Magnesium* (Wyman). OSRD Report M-292, 1944.
- 4.1222 *High Temperature Properties of Light Alloys (NA-137): Part II, Magnesium* (Wyman). OSRD Report M-292. 1944.
- 4.321 *Bending Strength of Round Magnesium Tubing*. Dow Chemical Company Report.

# CHAPTER 1

## GENERAL

### 1.1 Purpose and Use of Document

1.11 INTRODUCTION. Since many aircraft manufacturers supply airplanes for both commercial and military use, standardization of the requirements of the various Governmental procuring or certificating agencies is of direct benefit to the manufacturer. Although the types and purposes of military aircraft often differ greatly from those of commercial aircraft, necessitating certain differences in the structural requirements, the requirements for strength of materials and elements have for some time been nearly identical. This publication has therefore been prepared to eliminate the necessity for referring to different handbooks and bulletins in calculating the allowable stresses or minimum strength of typical structures. With a few exceptions (which are noted in the appropriate places) the material contained herein is acceptable to the Air Forces, Bureau of Aeronautics of the Navy, and the Civil Aeronautics Administration.

1.12 SCOPE OF DOCUMENT. Only the most commonly used materials and elements are included in this publication. Until a structural material or element has been used for some time and in considerable quantities, the strength properties will probably vary considerably as manufacturing processes are improved and modified. In such cases special rulings should be obtained by the manufacturer from the procuring or certificating agency. These rulings will be based upon specimen tests and will eventually form a basis for standard accepted strength properties.

In addition to the strength of the materials and elements themselves, there are contained herein some of the more commonly-used methods and formulas by which the strength of various structural components are calculated. In some cases the methods presented are empirical and subject to further refinement. Likewise, it is expected that additional material can be added from time to time as the methods of handling new problems become more uniform and reliable.

Engineers making use of the material contained herein are invited to submit comments and suggestions as to the expansion and improvement of the document. Such comments should be submitted directly to the Munitions Board, Washington 25, D. C. Attention ANC-5, Panel of the Subcommittee on Aircraft Design Criteria.

1.13 USE OF DESIGN MECHANICAL PROPERTIES. It is customary to assign minimum values to certain mechanical properties of materials for procurement specification purposes. In general, but not necessarily in all cases, the design mechanical properties given herein are based on these minimum values. The manner in which these design mechanical properties are to be used will depend on the type of structure being investigated and will be definitely specified in the detailed structural requirements of the procuring or licensing agencies. The use of the different design mechanical properties such as ultimate tensile strength, yield strength, etc., the factors of safety associated with them, and the arbitrary reductions in allowable stresses which may be considered necessary in particular cases, will not be taken up in detail herein, information of this sort being in the nature of specific requirements which do not affect the material properties as such.

### 1.2 Standard Structural Symbols

- A*—Area of cross section, square inches.
- a*—Subscript "allowable."
- B*—Slenderness ratio factor. (See equation 1:392.)
- b*—Width of sections; subscript "bending."
- br*—Subscript "bearing."
- C*—Circumference.
- c*—Fixity coefficient for columns; distance from neutral axis to extreme fiber; subscript "compression."
- cr*—Subscript "critical."
- D*—Diameter.
- d*—Depth or height; mathematical operator denoting differential.

- $E$ —Modulus of elasticity in tension; average ratio of stress to strain for stress below proportional limit.
- $e$ —Elongation, this factor being a measure of the ductility of the material and being based on a tension test; unit deformation or strain; eccentricity; subscript for Euler's formula; subscript "endurance."  
—The minimum distance from a hole centerline to the edge of the sheet.
- $E'$ —Effective modulus of elasticity.
- $E_c$ —Modulus of elasticity in compression; average ratio of stress to strain below proportional limit.
- $E_s$ —Secant modulus.
- $E_t$ —Tangent modulus.
- $F$ —Allowable stress.
- $f$ —Internal (or calculated) stress.
- $F_b$ —Allowable bending stress, modulus of rupture in bending.
- $f_b$ —Internal (or calculated) primary bending stress.
- $f_b'$ —Internal (or calculated) precise bending stress.
- $F_{be}$ —Endurance limit in bending.
- $f_{br}$ —Internal (or calculated) bearing stress.
- $F_{bru}$ —Ultimate bearing stress.
- $F_{brv}$ —Yield bearing stress.
- $F_c$ —Allowable compressive stress.
- $f_c$ —Internal (or calculated) compressive stress.
- $F_{cc}$ —Allowable crushing or crippling stress (upper limit of column stress for local failure).
- $F_{co}$ —Column yield stress (upper limit of column stress for primary failure).
- $F_{cp}$ —Proportional limit in compression.
- $F_{cu}$ —Ultimate compressive stress.
- $F_{cy}$ —Compressive yield stress.
- $F_n$ —Allowable normal stress.
- $f_n$ —Internal (or calculated) normal stress.
- $F_s$ —Allowable shearing stress.
- $f_s$ —Internal (or calculated) shearing stress.
- $F_{scr}$ —Critical shear stress for buckling of rectangular panels.
- $F_{se}$ —Endurance limit in torsion.
- $F_{sp}$ —Proportional limit in shear.
- $F_{st}$ —Modulus of rupture in torsion.
- $F_{su}$ —Ultimate stress in pure shear. This value represents the average shearing stress over the cross section.
- $F_t$ —Allowable tensile stress.
- $f_t$ —Internal (or calculated) tensile stress.
- $F_{tp}$ —Proportional limit in tension.
- $F_{tu}$ —Ultimate tensile stress (from tests of standard specimens).
- $F_{ty}$ —Tensile yield stress at which permanent strain equals 0.002 (from tests of standard specimens).
- $G$ —Modulus of rigidity.
- $g$ —
- $H$ —
- $h$ —Height or depth; especially the distance between centroids of chords of beams and trusses.
- $I$ —Moment of inertia.
- $i$ —Slope (due to bending) of neutral plane of a beam, in radians (1 radian = 57.3°).
- $I_p$ —Polar moment of inertia.
- $J$ —Torsion constant (=  $I_p$  for round tubes).
- $j$ —Stiffness factor =  $\sqrt{EI/P}$ .
- $K$ —A constant, generally empirical.
- $ksi$ —Kips (1,000 pounds) per square inch.
- $L$ —Length; subscript "lateral."
- $l$ —(Not used, to avoid confusion with numeral 1.)
- $M$ —Applied moment or couple, usually a bending moment.
- $m$ —
- $M_a$ —Allowable bending moment.
- $N$ —
- $n$ —Subscript "normal."
- $O$ —
- $o$ —
- $P$ —Applied load (total, not unit load).
- $p$ —Subscript "polar"; subscript "proportional limit."
- $P_a$ —Allowable load.
- $psi$ —Pounds per square inch.
- $Q$ —Static moment of a cross section.
- $q$ —
- $R$ —Stress ratio =  $f/F$ .
- $r$ —Radius.
- $S$ —Shear force.
- $s$ —Subscript "shear."
- $T$ —Applied torsional moment torque.
- $t$ —Thickness.
- $T_a$ —Allowable torsional moment.
- $U$ —Factor of utilization.
- $u$ —Subscript "ultimate."
- $V$ —
- $v$ —
- $W$ —
- $w$ —Specific weight, lb/cu. in.
- $X$ —
- $x$ —Distance along elastic curve of a beam.
- $Y$ —



$y$ —Deflection (due to bending) of elastic curve of a beam; distance from neutral axis to given fiber; subscript “yield.”

$Z$ —Section modulus,  $I/y$ .

$z$ —

$Z_p$ —Polar section modulus  $= I_p/y$  (for round tubes).

$\delta$  (delta)—Deflection.

$\phi$  (phi)—Angular deflection.

$\rho$  (rho)—Radius of gyration.

$\mu$  (mu)—Poisson's ratio.

' (prime)—In general denotes an “effective” or “precise” value.

### 1.3 Commonly Used Formulas

1.31 GENERAL. The formulas of the following sections are listed for reference purposes. The sign conventions generally accepted in their use are that quantities associated with tensile action (load, stress, strain, etc.) are considered as positive, and quantities associated with compressive action are considered as negative. When compressive action is of primary interest, however, it is sometimes convenient to consider the associated quantities to be positive.

#### 1.32 SIMPLE UNIT STRESSES

1.321  $f_t = P/A$  (tension).

1.322  $f_c = P/A$  (compression).

1.323  $f_b = My/I = M/Z$ .

1.324  $f_s = S/A$  (average direct shear stress).

1.325  $f_s = SQ/Ib$  (longitudinal or transverse shear stress).

1.326  $f_s = Ty/I_p$  (shear stress in round tubes due to torsion).

1.327  $f_s = T/2At$  (shear stress due to torsion in thin-walled structures of closed section. Note that  $A$  is the area enclosed by the median line of the section).

#### 1.33 COMBINED STRESSES (see sec. 1.535)

1.331  $f_n = f_c + f_b$  (compression and bending).

1.332  $f_{s_{max}} = \sqrt{f_s^2 + (f_n/2)^2}$  (compression bending, and torsion).

1.333  $f_{n_{max}} = f_n/2 + f_{s_{max}}$ .

#### 1.34 DEFLECTIONS (Axial)

1.341  $e = \delta/L$  (unit deformation or strain).

1.342  $E = f/e$  (this equation applies when  $E$  is to be found from tests in which  $f$  and  $e$  are measured).

1.343  $\delta = eL = (f/E)L$   
 $= PL/AE$  (this equation applies when the deflection is to be calculated using a known value of  $E$ )

#### 1.35 DEFLECTIONS (Bending)

1.351  $di/dx = M/EI$  (change of slope per unit length of beam, radians per unit length).

1.352  $i_2 = i_1 + \int_{x_1}^{x_2} (M/EI) dx$  = slope at point 2.

(The integral denotes the area under the curve of  $M/EI$  plotted against  $x$ , between the limits  $x_1$  and  $x_2$ )

#### 1.353

$y_2 = y_1 + i_1(x_2 - x_1) + \int_{x_1}^{x_2} (M/EI)(x_2 - x) dx$

= deflection at point 2. (The integral denotes the area under a curve having ordinates equal to  $M/EI$  multiplied by the corresponding distances to point 2, plotted against  $x$ , between the limits  $x_1$  and  $x_2$ )

1.353a  $y_2 = y_1 + \int_{x_1}^{x_2} i dx$  = deflection at point 2.

(The integral denotes the area under the curve of  $(i)$  plotted against  $x$ , between the limits  $x_1$  and  $x_2$ )

#### 1.36 DEFLECTIONS (Torsion)

1.361  $d\phi/dx = T/GJ$  (change of angular deflection or twist per unit length of member, radians per unit length).

1.362  $\phi = \int_{x_1}^{x_2} (T/GJ) dx$  = total twist over a

length from  $x_1$  to  $x_2$ . (The integral denotes the area under the curve of  $T/GJ$  plotted against  $x$ , between the limits  $x_1$  and  $x_2$ .)

1.362a  $\phi = TL/GJ$  (used when torque  $T$  is constant over length  $L$ ).

#### 1.37 TRANSVERSE DEFORMATIONS

1.371  $\mu = e_L/e = \frac{\text{unit lateral deformation}}{\text{unit axial deformation}}$   
 (Poisson's ratio)

1.372  $Ee_x = f_x - \mu f_y$ .

1.373  $Ee_y = f_y - \mu f_x$ .

#### 1.38 BASIC COLUMN FORMULAS

1.381  $F_c = c\pi^2 E / (L/\rho)^2$  (Euler formula for long columns).

$= \pi^2 E / (L'/\rho)^2$  where  $L' = L/\sqrt{c}$ .

1.381a  $F_c = c\pi^2 E' / (L/\rho)^2$  (modified Euler formula for short columns).

1.382  $F_c = F_{co} \{1 - K[(L'/\rho)/\pi\sqrt{E/F_{co}}]^n\}$  (general parabolic formula).

1.383  $F_c = F_{co} [1 - F_{co}(L'/\rho)^2/4\pi^2 E]$  (2.0 parabola—Johnson formula).

1.384  $F_c = F_{co} \{1 - 0.3027 [(L'/\rho)/\pi\sqrt{E/F_{co}}]^{1.5}\}$  (1.5 parabola).

- 1.385  $F_c = F_{co} [1 - 0.385(L'/\rho)/\pi\sqrt{E/F_{co}}]$  (1.0 parabola—straight line formula).
- 1.39 BASIC COLUMN FORMULAS (Non-dimensional)
- 1.391  $R_a = F_c/F_{co}$  (allowable stress ratio).
- 1.392  $B = (L'/\rho)/\pi\sqrt{E/F_{co}}$  (slenderness ratio factor).
- 1.393  $R_a = (1/B)^2$  (Euler formula).
- 1.394  $R_a = 1 - KB^n$  (general parabolic formula).
- 1.395  $R_a = 1 - 0.25B^2$  (2.0 parabola—Johnson formula).
- 1.396  $R_a = 1 - 0.3027B^{1.5}$  (1.5 parabola).
- 1.397  $R_a = 1 - 0.385B$  (1.0 parabola—straight line formula).

## 1.4 Basic Principles and Definitions

1.41 GENERAL. It is assumed that engineers using this document are thoroughly familiar with the basic principles of strength of materials, such as can be found in any standard text book on this subject. A brief summary of such material is presented here for the sake of uniformity and to emphasize certain principles of special importance. The design mechanical properties of various metals and elements are given in the tables in each chapter.

### 1.42 STRESS

1.421 *General.* The term stress as used herein always implies a force per unit area and is a measure of the intensity of the force acting on a definite plane passing through a given point. (See equations 1.321 and 1.322.) The stress distribution may or may not be uniform, depending on the nature of the loading condition. For example, tensile stresses as found from equation 1.321 are considered to be uniform, while the bending stress determined from equation 1.323 refers to the stress at a point located at a distance  $y$  from the neutral axis. Obviously the stress over the cross section of a member subjected to bending is not uniform. Likewise the shear stresses caused by a shearing load are not uniform. (Equation 1.324 gives the average stress.)

1.422 *Normal and shear stresses.* The stresses acting at a point in any stressed member can be resolved into components acting on planes through the point.

The normal and shear stresses acting on any particular plane are the stress components perpendicular and parallel, respectively, to the plane. A simple conception of these stresses is that normal stresses tend to pull apart (or press

together) adjacent particles of the material, while shear stresses tend to cause such particles to slide on each other.

### 1.43 STRAIN

1.431 *Axial strain.* This term refers to the elongation, per unit length, of a member or portion of a member in a stressed condition. (See equation 1.341.) The term "strain" should not be used in place of the terms "elongation" and "deflection."

1.432 *Lateral strain.* The axial strain of a member is always accompanied by a lateral strain of opposite sign. The ratio of the lateral strain to the axial strain is called Poisson's ratio and is designated as  $\mu$ . The value of  $\mu$ , is usually between 0.25 and 0.33 for steel and the aluminum alloys.

1.433 *Shearing strain.* If a square element of uniform thickness is subjected to pure shear there will be a displacement of each side of the element relative to the opposite side. The shearing strain is obtained by dividing this displacement by the distance between the sides of the element. It should be noted that shearing strain is obtained by dividing a displacement by a distance at right angles to the displacement whereas axial strain is obtained by dividing the deformation by a length measured in the same direction as the deformation.

### 1.44 TENSILE PROPERTIES

1.441 *General.* When a specimen of a certain material is tested in tension using the standard testing procedures of reference 1.441, it is customary to plot the results of such a test as a "stress-strain diagram." This diagram forms the basis for most strength specifications and should be thoroughly understood and frequently applied by all engineers. Typical tensile diagrams, not to scale, are shown in figure 1.441. Typical stress-strain diagrams drawn to scale appear in appropriate chapters for the general information of the users of this document. It should be noted that the strain scale is nondimensional, while the stress scale is in pounds per square inch. The important physical properties which can be shown on the stress-strain diagram are discussed in the following sections.

1.442 *Modulus of elasticity (E).* Referring to figure 1.441, it will be noted that the first part of the diagram is substantially a straight line. This indicates a constant ratio between stress and strain over that range. The numerical value of the ratio is called the Modulus of Elasticity, denoted by  $E$ . It will be noted that  $E$  is the slope

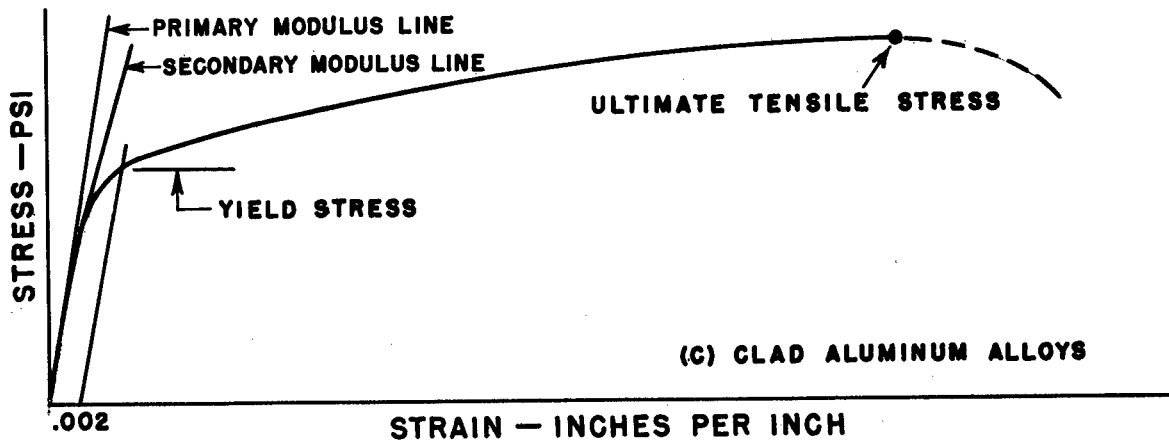
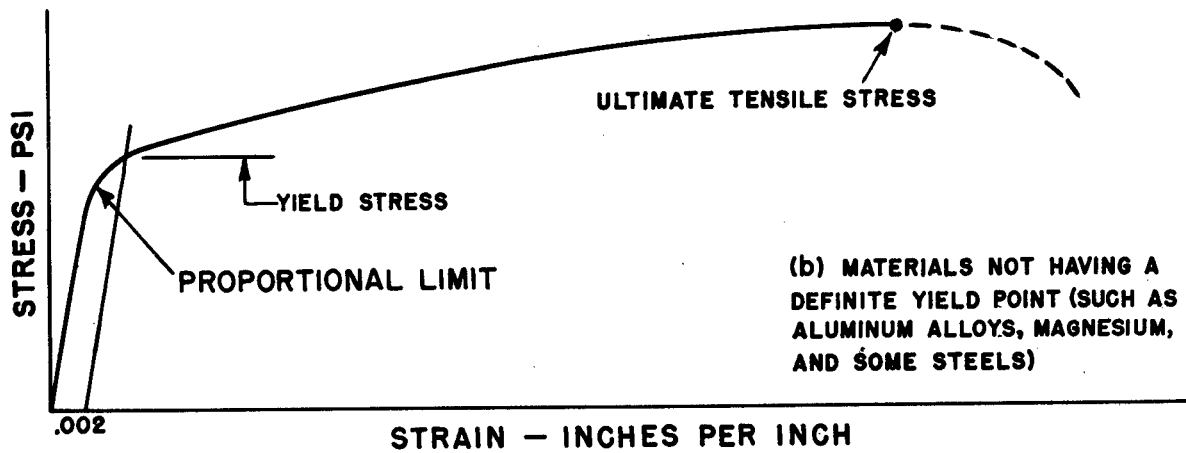
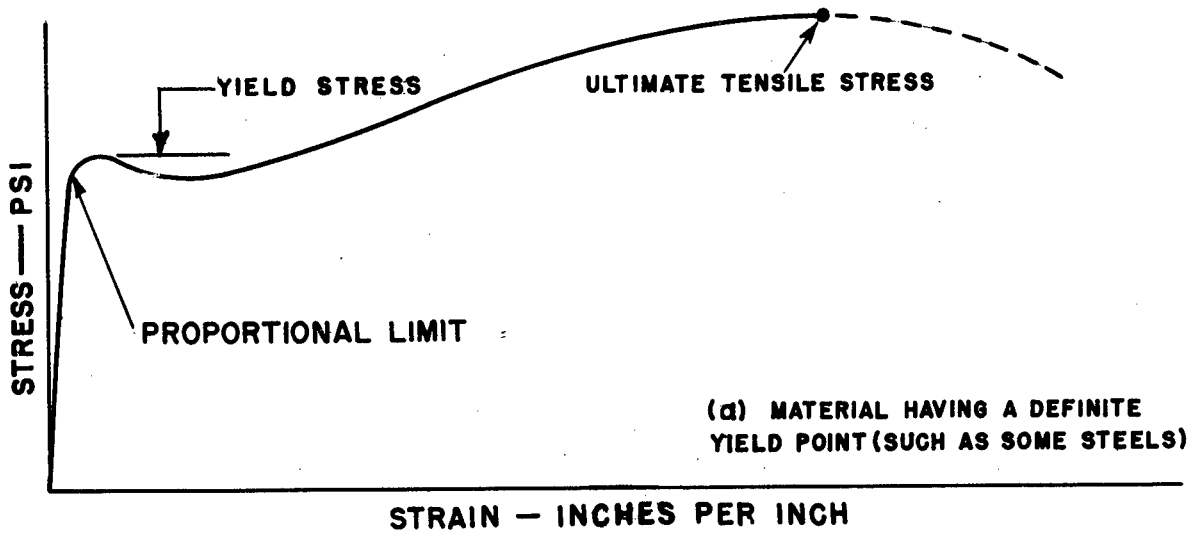


Figure 1.441. Typical tensile stress-strain diagrams.

of the straight portion of the stress-strain diagram and is determined by dividing the stress (in pounds per square inch) by the strain (which is nondimensional). (See equation 1.342.) Therefore,  $E$  has the same dimensions as a stress; in this case pounds per square inch. A useful conception of  $E$  is "the stress at which the member would have elongated a distance equal to its original length (assuming no departure from the straight portion of the stress-strain diagram)." This can be easily understood from equation 1.342 by considering that  $\delta=L$  in equation 1.341, making the strain  $e$  equal to 1.0.

Other moduli that are often of interest are the tangent modulus  $E_t$ , and the secant modulus  $E_s$ . The tangent modulus is the slope of the stress-strain diagram at a point corresponding to a given stress while the secant modulus is the slope of a line drawn through the same point and the origin.

Clad aluminum alloys have two separate modulus values, as indicated in the typical curve presented in figure 1.441. The initial modulus is the same as for the other aluminum alloys, and holds only up to the proportional limit of the relatively soft covering. Immediately above this point there is a short transition range and the material then exhibits a secondary modulus up to the proportional limit of the stronger core material. This secondary modulus is the slope of the second straight line portion of the diagram. Both values of the modulus are based on the gross area of the piece, core plus covering.

1.443 *Tensile proportional limit ( $F_{tp}$ )*. Since it is practically impossible to determine the stress at which the stress-strain diagram begins to depart from a straight line, it is customary to assign a small value of permanent strain for this purpose. In this document the limit of proportionality will be taken as the stress at which the stress-strain diagram departs from a straight line by a strain of 0.0001. This property or characteristic of a material gives an indication of the type of stress-strain diagram which applies in the working range. It also indicates the stress beyond which the standard value of  $E$  cannot be accurately applied. This is of special interest in the analysis of redundant structures.

1.444 *Tensile yield stress ( $F_{ty}$ )*. The stress-strain diagrams for some steels show a sharp break at a stress considerably below the ultimate tensile stress. At this critical stress the material elongates considerably with little or no increase in stress. (See fig. 1.441.) The stress at which this

takes place is referred to as the yield point. Non-ferrous metals, and some steels do not show this sharp break but yield more gradually so that there is no definite yield point. This condition is illustrated in figure 1.441. Since permanent deformations of any appreciable amount are undesirable in most structures, it is customary to adopt an arbitrary amount of permanent strain that is considered admissible for general purposes. The value of this strain has been established by material testing engineers as 0.002, and the corresponding stress is called the *yield stress*. For practical purposes this may be determined from the stress-strain diagram by drawing a line parallel to the straight or elastic portion of the curve through a point representing zero stress and 0.002 strain. (See fig. 1.441.) The yield stress is taken as the stress at the intersection of this straight line with the stress-strain curve.

1.445 *Ultimate tensile stress ( $F_{tu}$ )*. Figure 1.441 shows how the ultimate tensile stress is determined from the stress-strain diagram. It is simply the stress at the maximum load reached in the test. It should be noted that all stresses are based on the original cross-sectional area of the test specimen, without regard to the lateral contraction of the specimen which actually occurs during the test. The ultimate tensile stress is commonly used as a criterion of the strength of the material, but it should be borne in mind that most modern aircraft structures have relatively few members which are critical in tension; consequently, other strength properties may often be more important.

## 1.45 COMPRESSIVE PROPERTIES

1.451 *General*. The results of compression tests can be plotted as stress-strain diagrams similar to those shown in figure 1.441 for tension. The preceding remarks (with the exception of those pertaining to ultimate stress) concerning the specific tensile properties of the material apply in a similar manner to the compressive properties. It should be noted that the moduli of elasticity in tension and compression are approximately equal for most of the commonly used structural materials. Special considerations concerning the ultimate compressive stress are taken up in the following section. An example of a method of obtaining compressive strength properties of thin sheet material is outlined in reference 1.451.

1.452 *Ultimate compressive stress ( $F_{cu}$ )*. It is difficult to discuss this property without reference

to column action. Almost any piece of material, unless very short, tends to buckle laterally as a column under compressive loadings, and the load at failure usually depends on the relation of the length of the piece to its cross-sectional dimensions. Column failure cannot occur, however, when a piece is very short in comparison with its cross-sectional dimensions, or when it is restrained laterally by external means. Under these conditions some materials such as stone, wood, and a few metals will fail by fracture, thus giving a definite value for the ultimate compressive stress. Most metals, however, are so ductile that no fracture is encountered in compression. Instead of fracturing, the material yields and swells out, so that the increasing area continues to support the increasing load. It is almost impossible to select a value for the ultimate compressive stress of such materials without having some arbitrary criterion. For wrought metals it is common practice to assume that the ultimate compressive stress is equal to the ultimate tensile stress. For some cast metals which are relatively weak in tension, an ultimate compressive stress higher than the ultimate tensile stress may be obtained from tests on short compact specimens. When tests are made on such specimens having an  $L/\rho$  approximately equal to 12, the ultimate stress so obtained is called the block compressive stress.

#### 1.46 SHEAR PROPERTIES

1.461 *General.* The results of torsion tests on round tubes or round solid sections are sometimes plotted as torsion stress-strain diagrams. The modulus of elasticity in shear as determined from such a diagram is a basic shear property. Other properties, such as the proportional limit and ultimate shearing stress, cannot be treated as basic properties because of the "form factor" effects.

1.462 *Modulus of rigidity ( $G$ ).* This property is the ratio of the shearing stress to the shearing strain at low loads, or simply the initial slope of the stress-strain diagram for shear. It is also called the modulus of elasticity in shear. The relation between this property, Poisson's ratio, and the modulus of elasticity in tension, is expressed for homogeneous materials by the following equation:

$$G = E/2(1 + \mu) \text{-----} (1.4621)$$

This corresponds to the value  $E$  and will apply in calculating the shear deflection of webs, provided that no wrinkling occurs.

1.463 *Proportional limit in shear ( $F_{sp}$ ).* This property is of particular interest in connection with formulas which are based on considerations of perfect elasticity, as it represents the limiting value of shearing stress to which these formulas can be accurately applied. As previously noted, this property cannot be determined directly from torsion tests. The results of research at the National Bureau of Standards show that the ratio of the proportional limit in shear to the proportional limit in tension can be assumed to be approximately 0.55 for the commonly used materials.

1.464 *Yield and ultimate stresses in shear.* These properties, as usually obtained from torsion tests, are not strictly basic properties as they will depend on the shape of the test specimen. In such cases they should be treated as moduli and should be used only with specimens which are geometrically similar to those from which the test results were obtained.

#### 1.47 CREEP AND STRESS-RUPTURE PROPERTIES

1.471 *General.* The results of tests of materials under a constant load at elevated temperatures are usually initially plotted as strain versus time (creep) up to the time of rupture. However, many combinations of the data obtained in these tests are possible and have resulted in many different types of plots. Data included in this publication are as described in the sections below. A typical plot of creep-rupture data is shown in figure 1.471. The strain indicated in this curve includes the initial instantaneous deformation due to loading. From this curve are obtained the stress-rupture curve, the minimum creep curve, the total deformation curve, and the other parameters shown in figures 3.1221 (a) to 3.1221 (l).

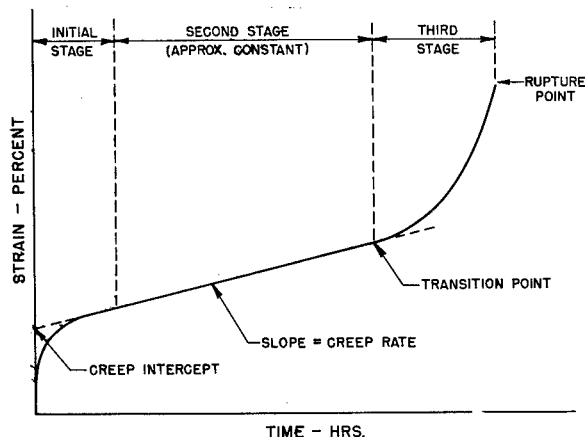


Figure 1.471. Typical creep-rupture curve.

1.472 *Total creep.* This value is defined as the total strain at any given time including initial strain. It is given in percent and may be used to estimate the deformation or deflection of structural parts for given loads and temperatures.

1.473 *Minimum creep rate.* After an initial large strain due to loading, the rate of strain in a creep specimen usually gradually decreases to a constant value (except for high stress), for a time dependent on the test conditions. This strain rate is the minimum encountered in the test and is defined as the creep rate.

1.474 *Transition point.* Subsequent to the constant creep rate described in the previous section an increase in creep rate occurs, in general, which continues up to the rupture point of the material. The inflection point between the constant creep and increasing creep rate is defined as the transition point. Failure generally occurs in a relatively short time after the transition point. Transition points may not occur at very low stresses or may not be definable at very high stresses.

1.475 *Rupture stress.* The stress at which rupture will occur under constant load conditions is defined as the rupture stress. This stress varies inversely with time for constant temperature conditions. Rupture stress data are generally used in design if the amount of deformation allowable is not the critical factor.

#### 1.48 FATIGUE PROPERTIES

1.481 *General.* The results of fatigue tests are usually plotted as stress versus the number of cycles needed to cause failure. This stress is usually the maximum stress in a single cycle. Many variations of the common completely reversed stressing are used, however, in such cases the stress description is not complete if the maximum stress only is recorded. Figure 1.481 indicates the type of stressing which might occur and indicates some of the parameters which affect the fatigue life of a material under fluctuating stresses.

1.482 *Stress.* The stress cycle through which a material is subjected may be of several types even in the commonly accepted sinusoidal variations shown in figure 1.481. To completely describe the stress history the following definitions of stress conditions are used, all of which may affect the fatigue life, either independently or in conjunction with one or more of the other conditions:

1.4821 *Maximum stress* is the highest algebraic stress reached in a single cycle.

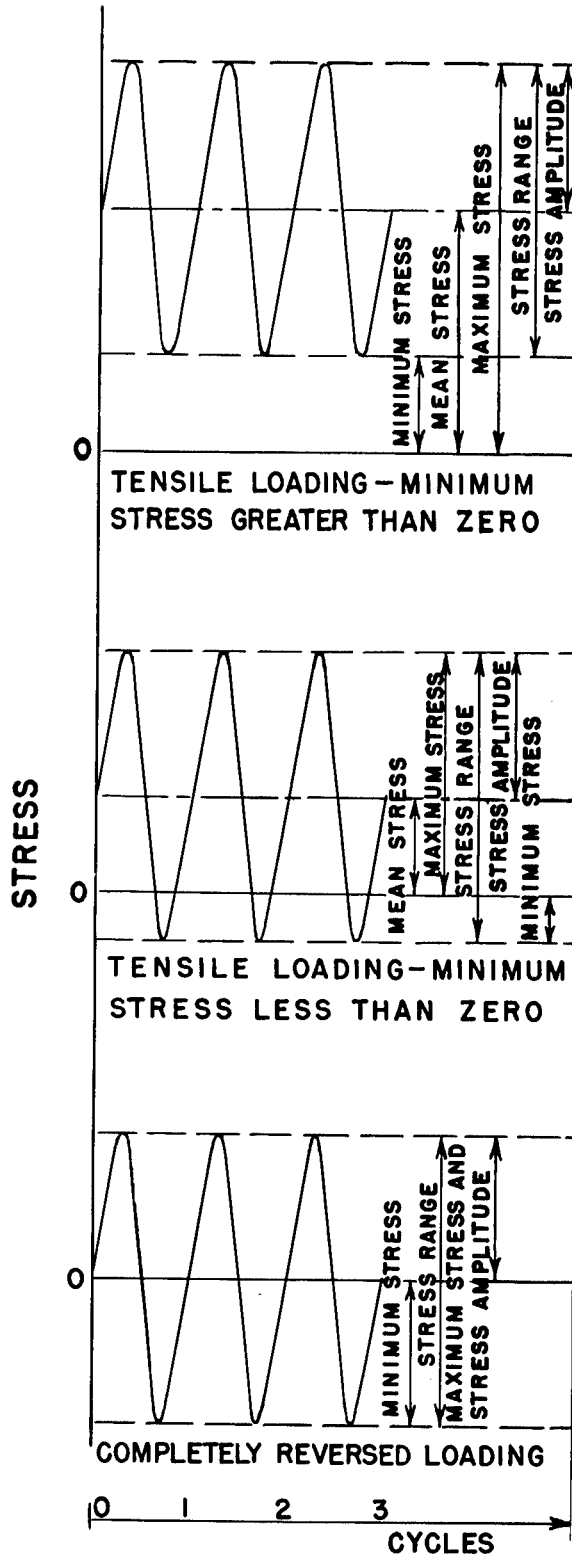


Figure 1.481. Typical fatigue loadings.

1.4822 *Minimum stress* is the lowest algebraic stress reached in a single cycle.

1.4823 *Mean stress* is the stress midway be-

tween the maximum and minimum stress. In the completely reversed test this stress is zero.

1.4824 *Stress range* is the stress variation between maximum and minimum.

1.4825 *Stress amplitude* is the stress variation between mean and maximum or between mean and minimum and is one-half the stress range.

## 1.5 Types of failures

1.51 **GENERAL.** In the following discussion the term "failure" will usually denote actual rupture of the member, or the condition of the member when it has just attained its maximum load.

### 1.52 MATERIAL FAILURES

1.521 *General.* Fracture of a material may occur by either a *separation* of adjacent particles across a section perpendicular to the direction of loading, or by a *sliding* of adjacent particles along other sections. In some cases the mechanism of failure includes both of these actions. For instance, in a simple tension test sliding action along inclined sections may occur first with a consequent reduction in the cross-sectional area of the specimen. This may result in strain hardening of the material so that the resistance to sliding is increased, and the final failure may occur by separation of the material across a section perpendicular to the direction of the loading.

1.522 *Direct tension or compression.* This type of failure is associated with the ultimate tensile or compressive stress of the material. For compression it can apply only to members having large cross-sectional dimensions as compared to the length in the direction of the load. (See also sec. 1.452.)

1.523 *Shear.* Pure shear failures are usually obtained only when the shear load is transmitted over a very short length of the member. This condition is approached in the case of rivets and bolts. In cases where the ultimate shear stress is relatively low a pure shear failure may result, but in general a member subjected to a shear load fails under the action of the resulting normal stresses (equation 1.333), usually the compressive stresses. The failure of a tube in torsion, for instance, is not usually caused by exceeding the allowable shear stress, but by exceeding a certain allowable normal compressive stress which causes the tube to buckle. It is customary, for convenience, to determine the allowable stresses for members subjected to shear in the form of shear stresses. Such allowable shear stresses are therefore an indirect measure of the stresses actually causing failure.

1.524 *Bearing.* The failure of a material in bearing may consist of crushing, splitting, or progressive rapid yielding in the region where the load is applied. Failure of this type will depend, to a large extent, on the relative size and shape of the two connecting parts. The allowable bearing stress will not always be applicable to cases in which one of the contacting members is relatively thin. It is also necessary, for practical reasons, to limit the working bearing stress to low values in such cases as joints subjected to reversals of load or in bearings between movable surfaces. These special cases are covered by specific rulings of the procuring or licensing agencies, involving the use of higher factors of safety in most cases.

1.525 *Bending.* For compact sections not subject to instability, a bending failure can be classed as a tensile or compressive failure caused by exceeding a certain allowable stress in some portion of the specimen. It is customary to determine, experimentally, the "modulus of rupture in bending," which is a stress derived from test results through the use of equation 1.323 in which case  $M$  is the value of bending moment which caused failure. If not determined experimentally, the value of the modulus of rupture in bending may be assumed equal to the ultimate tensile stress when instability is not critical. Since equation 1.323 is based on assumptions which are not always fulfilled at failure, the modulus at failure cannot be considered as the actual stress at the point of rupture. This should be borne in mind in dealing with combined stresses, such as bending and compression, or bending and torsion.

1.526 *Failure due to stress concentrations.* The static strength properties listed for various materials were determined on machined specimens containing no notches, holes, or other avoidable stress raisers. In the design of aircraft structures such simplicity is unattainable, and stress distributions are not of the uniform quality obtained in the specimen tests. Consideration must be given to this condition since maximum stresses in a material, and not average stresses, are the critical factor in design. The effects of stress raisers vary, and references to available specific data are given in the sections pertaining to each material.

1.527 *Failure due to fatigue.* Although the component parts of airplane structures are usually designed for static load conditions, they are subjected in service to repeated loads. It is well known that the strength of a material under

repeated loads is less than that which would be obtained under static loading. This phenomenon of the decreased strength of a material under repeated loading is commonly called fatigue. Stress raisers, such as abrupt changes in cross section, holes, notches and re-entrant corners, cause a much greater effect on the fatigue strength than they do on static strength. The local high stress concentrations caused by such stress raisers are often greatly in excess of the nominal calculated stress on the part and consequently it is at such locations that fatigue fractures usually begin. Other factors of major importance in fatigue are the range of a repeated stress cycle, from maximum to minimum stress, and the mean stress in the stress cycle. In the following chapters of this document, fatigue data are presented for various materials. These data were obtained in various types of repeated-load tests and are included for general information. They are not to be used as allowable stress values unless their applicability to the case at hand has been established.

1.528 *Failure from combined stresses.* In combined stress conditions where failure is not due to buckling or instability it is necessary to refer to some theory of failure. The "maximum shear" theory has received wide acceptance as a simple working basis in the case of ductile materials. It should be noted that this theory interprets failure as the first yielding of the material, so that any extension of the theory to cover conditions of final rupture must be based on the experience of the designer. The failure of brittle materials under combined stresses can generally be treated by the "maximum stress" theory.

### 1.53 INSTABILITY FAILURES

1.531 *General.* Practically all structural members such as beams and columns, particularly those made from thin material, are subject to failure through instability. In general, instability can be classed as: (1) Primary, or (2) local. For example, the failure of a tube under compression may occur either through lateral deflection of the tube as a column (primary instability), or by collapse of the tube wall at a stress lower than that required to produce a general column failure. Similarly, an I-beam may fail by a general sidewise deflection of the compression flange, or by local wrinkling of thin outstanding flanges. It is obviously necessary to consider both types of failures unless it is apparent that the critical load

for one type is definitely less than that for the other type.

Instability failures may occur in either the elastic range (below the proportional limit) or in the plastic range (above the proportional limit). To distinguish between these two types of action it is not uncommon to refer to them as elastic instability failures and plastic instability failures, respectively. It is important to note that instability failures are not usually associated with the ultimate stresses of the material. This should be borne in mind when correcting test results for material variations. It also has a bearing on the choice of a material for a given type of construction as the "strength-weight ratio" will be determined from different physical characteristics when this type of failure can be expected. For materials which have a very small spread between the proportional limit and the yield stress, the plastic instability type of failure occurs in such a narrow range that it is not of much importance, but in materials which have a considerable spread between these two properties, the plastic instability type of failure may be equally as important as the elastic type.

In studying any structural member it is important to avoid confusion between the different types of failure, particularly where instability is expected to be important. In general, most members should be investigated first from the standpoint of failures of material. They should then be checked separately for their resistance to primary instability failure. Members which are suspected of being weak in resisting local instability should also be checked for this third possible type of failure. Whichever type of failure gives the lowest strength should be used as the criterion in design.

1.532 *Instability failures under compressive loadings.* Failures of this type are discussed in section 1.6 (columns).

1.533 *Bending instability failures.* Failures of round tubes of usual sizes when subjected to bending are usually of the plastic instability type. In such cases the criterion of strength is the modulus of rupture as derived from test results through the use of equation 1.323. Elastic instability failures of thin-walled tubes having high  $D/t$  ratios are treated in later sections.

1.534 *Torsional instability failures.* The remarks of the preceding section apply in a similar manner to round tubes under torsional loading.



In such cases the modulus of rupture in torsion is derived through the use of equation 1.326.

1.535 *Failure under combined loadings.* For combined loading conditions in which failure is caused by buckling or instability, no general theory exists which will apply in all cases. It is convenient, however, to represent such conditions by the use of "stress ratios," which can be considered as nondimensional coefficients denoting the fraction of the allowable stress or strength which is utilized or which can be developed under special conditions. For simple stresses the stress ratio can be expressed as—

$$R=f/F \text{-----} (1.5351)$$

where

$f$ =applied stress.

$F$ =allowable stress.

Note that the "margin of safety" as usually expressed is given by the equation:

$$\text{M. S.} = 1/R - 1.0 \text{-----} (1.5352)$$

Considering the case of combined loadings, the general conditions for failure can be expressed by equations of the following type:

$$R_1^x + R_2^y + R_3^z + \dots = 1.0 \text{---} (1.5353)$$

In this equation  $R_1$ ,  $R_2$ , and  $R_3$  may denote, for instance, the stress ratios for compression, bending, and shear, and the exponents  $x$ ,  $y$ , and  $z$  define the general relationship of the quantities. This equation may be interpreted as indicating that failure will occur only when the sum of the stress ratios is equal to or greater than one. An advantage of this method is that the formula yields correct results when only one loading condition is present. Consequently it tends to give good results when any one loading condition predominates. It also permits test data to be plotted in nondimensional form, which is a decided advantage.

In many cases it is convenient to deal directly with "load ratios" rather than stress ratios. The load ratio is simply the ratio of the applied load to the allowable load and is equal to the corresponding stress ratio.

Considering only two loading conditions, such as bending and torsion, equation 1.5353 can be plotted as a single interaction curve of  $R_b$  against  $R_s$ . Likewise, in the case of combined bending and compression,  $R_c$  can be plotted against  $R_b$ . When all three conditions exist, the equation represents

an interaction surface, which can be plotted as a family of curves. Typical curves corresponding to various exponents are shown in figure 1.535. The general significance of equation 1.5353 and figure 1.535 is that the addition of a second loading condition will lower the percentage of the allowable stress which may be utilized in the original loading condition. If the exponents approach infinity, the curve of figure 1.535 will approach the lines  $R_1=1.0$  and  $R_2=1.0$ , indicating that the two loading conditions have no effect on each other.

When only two stress-ratios are involved and when the two different applied stresses remain in constant proportion, the margin of safety of the member may be determined from figure 1.535 by the following method:

- (1) Locate the point on the chart representing the applied values of  $R_1$  and  $R_2$  computed from the applied stresses (illustrated as point (1) on fig. 1.535).
- (2) Draw a straight line through this point and the origin (shown as a diagonal dotted line on fig. 1.535).
- (3) Extend this line to intersect the proper stress-ratio curve (corresponding to the condition under consideration) at point (2).
- (4) Read the allowable values  $R_{1a}$  and  $R_{2a}$  as the ordinate and abscissa, respectively, of point (2).
- (5) The *factor of utilization* or *strength ratio* is obtained as the ratio of the applied to the allowable value of either stress ratio as follows:

$$\bar{U} = R_1/R_{1a} = R_2/R_{2a} \text{-----} (1.5354)$$

- (6) The true margin of safety then can be computed from the following equation:

$$\text{M. S.} = \frac{1}{\bar{U}} - 1 \text{-----} (1.5355)$$

Note that when the following stress ratio expressions are used, the margins of safety can be computed as indicated

For  $R_1 + R_2 = 1$ ,

$$\text{M. S.} = \frac{1}{(R_1 + R_2)} - 1$$

For  $R_1^2 + R_2^2 = 1$

$$\text{M. S.} = \frac{1}{\sqrt{R_1^2 + R_2^2}} - 1$$

Other M. S. formulas can, of course, be determined for the more complicated stress ratio expressions.

The general formula for the margin of safety stated analytically for interaction equations where any or all of  $x$ ,  $y$ , and  $z$  are 1 or 2 but no other figure (except one term may be missing) is as follows:

$$\text{M. S.} = \frac{2}{[R' + \sqrt{(R')^2 + 4(R'')^2}] - 1}$$

Here the  $R'$  designates the sum of all first power ratios;  $(R')^2$  is the square of the same sum; and  $(R'')^2$  the sum of the squares of all second-power ratios. The table gives all combinations:

Interaction formula	Margin of safety
$R_1 + R_2^2 = 1.0$	$\frac{2}{(R_1 + \sqrt{R_1^2 + 4R_2^2})} - 1$
$R_1 + R_2 + R_3 = 1.0$	$\frac{1}{(R_1 + R_2 + R_3)} - 1$
$R_1 + R_2 + R_3^2 = 1.0$	$\frac{2}{(R_1 + R_2 + \sqrt{(R_1 + R_2)^2 + 4R_3^2})} - 1$
$R_1 + R_2^2 + R_3^2 = 1.0$	$\frac{2}{[R_1 + \sqrt{R_1^2 + 4(R_2^2 + R_3^2)}]} - 1$
$R_1^2 + R_2^2 + R_3^2 = 1.0$	$\frac{1}{\sqrt{R_1^2 + R_2^2 + R_3^2}} - 1$

The practical application of equation 1.5353 will be taken up in the following chapters.


## 1.6 Columns

1.61 GENERAL. A theoretical treatment of columns can be found in standard textbooks on the strength of materials. The problems confronting the designer include, however, many points which are not well defined by theory and which frequently cause some confusion. These will be taken up in this section. Actual strengths of columns of various types are given in subsequent chapters.

### 1.62 PRIMARY INSTABILITY FAILURE

1.621 *General.*—A column may fail through primary instability by bending laterally (stable sections) or by twisting about some axis parallel to its own axis. This latter type of primary failure is particularly common to columns having unsymmetrical open sections. The twisting failure of a closed section column is precluded by its inherently high torsional rigidity. Since the available information on twisting instability is somewhat limited it may be advisable to conduct tests on all columns subject to this type of failure.

1.622 *Long columns.* (Stable Sections). The Euler formula for long columns which fail by lateral bending is given by equation 1.381. No explanation of this classical formula need be offered, as its derivation can be found in many standard textbooks on the strength of materials. The value to be used for the restraint coefficient,  $c$ ,

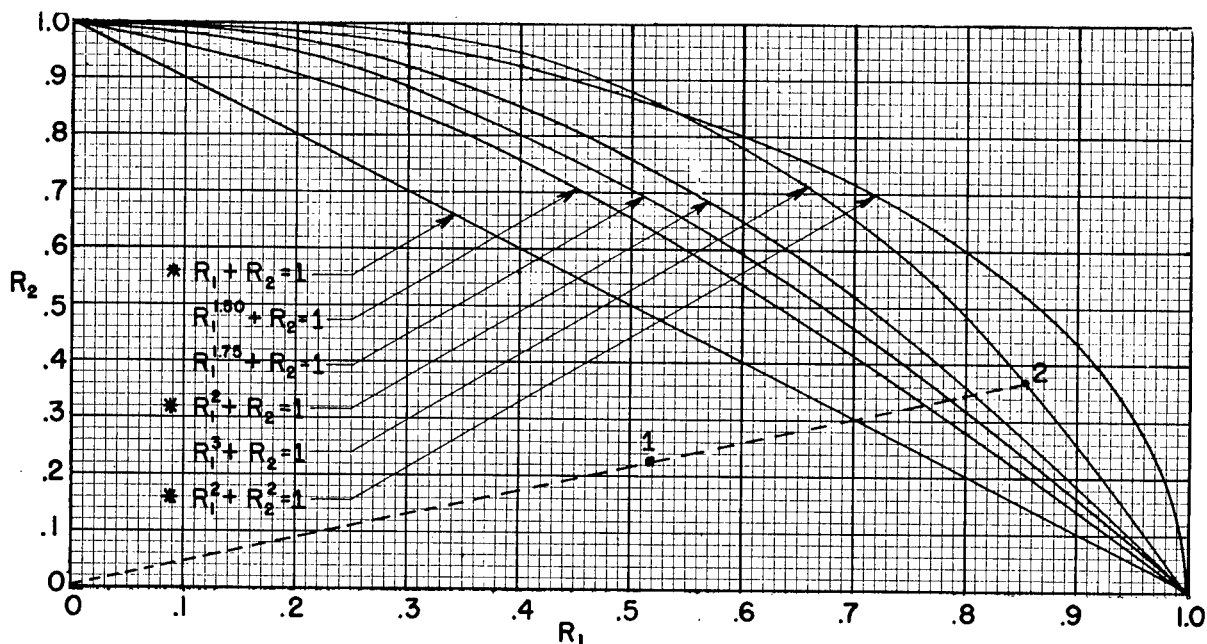

\* REFER TO SECTION 1.535 FOR ANALYTICAL MARGIN OF SAFETY

Figure 1.535. Typical interaction curves for combined loading conditions.

depends on the degree of end fixation. The true significance of the restraint coefficient is best understood by considering the end restraint as modifying the effective column length, as indicated in equation 1.381. For a pin-ended column having zero end restraint  $c=1.0$  and  $L'=L$ . A fixity coefficient of 2 corresponds to a reduction of the effective length to  $1/\sqrt{2}$  or 0.707 times the total length.

1.623 *Short columns* (Stable Sections). If the length of a column is reduced below a certain critical value, failure in lateral bending will occur at loads below those predicted by the Euler formula. This is in a great part due to a reduction in the effective value of  $E$  caused primarily by changes in the slope of the stress-strain diagram and secondarily by unavoidable eccentricities. In this region the test results show more scatter than in the Euler range and empirical or semi-empirical formulas for predicting the allowable column stress are often adopted. When a definite eccentricity exists, the critical column loads are reduced due to the combined effects of axial load and bending. Special formulas for such cases can be found in standard textbooks and handbooks.

Although many types of formulas have been devised to cover the short-column range, it has been customary, in aircraft work, to use the Johnson formula for round steel tubes and the straight line formula for round aluminum alloy tubes; these formulas are used in this document.

It will be noted that the above column formulas are of the general form given by equation 1.382. For example, the straight line formula is a special case of equation 1.382 in which the exponent  $n$  is equal to 1.0. In a similar manner the Johnson formula can be obtained from equation 1.382 by setting  $n$  equal to 2.0. The above equations strictly apply only to round tube sections as they were derived from tests on such sections. In many cases, however, they will be found to be satisfactory for sections of other shapes when local instability is not critical.

Short column failure can also be expressed by the modified Euler formula in which the elastic modulus is replaced by an effective modulus,  $E'$ , as in the following equation:

$$F_c = \pi^2 E' / (L'/\rho)^2 \text{-----} (1.6231)$$

This equation has come to have much practical importance in recent years in determining the short column curve; it is of particular interest

to note that an effective modulus equal to the tangent modulus can usually be used to compute failing stresses. The value of the effective modulus at any given compressive stress,  $F_c$ , can be determined from stress-strain curves for the material.

1.624 *Column yield stress* ( $F_{co}$ ). The upper limit of the allowable column stress for primary failure is called the *column yield stress* and will be designated  $F_{co}$ . It can be determined by extending the "short-column" curve to a point corresponding to zero length, ignoring any tendency of the curve to rise rapidly or "pick-up" for very short lengths. The short-column curve used in determining  $F_{co}$  should be obtained from tests on specimens having geometrical proportions such that local failure is precluded except for very low values of  $L'/\rho$ .

When the column yield stress is reached, the walls of the column will tend to buckle unless restrained by extreme shortness, or by the application of lateral restraining forces. In some cases, however, if the specimen has not been allowed to buckle, the stress may be increased considerably above this value. Due to the danger of buckling when the column yield stress is approached, the latter should be considered as the limiting stress for all columns.

The column yield stress is mainly determined by the nature of the compressive stress-strain diagram of the material. When the material has a definite yield point in compression, this value may be assumed for the column yield stress. Few aircraft materials, however, have a sharply defined yield point. In such cases it is usually possible to determine the column yield stress as a function of either the tensile or compressive yield stress. For example  $F_{co}$  for round steel tubes is approximately equal to 1.06 times the tensile yield stress; whereas, by reference 1.624,  $F_{co}$  for some aluminum alloys, see table 3.21, is approximately equal to  $F_{cy} (1 + F_{cy}/200,000)$ .

Column yield stresses for the various materials are given in the appropriate sections.

### 1.63 NONDIMENSIONAL COLUMN CURVES FOR PRIMARY FAILURE

1.631 *General*. On account of the many factors involved it is often difficult to predict the effects of possible material variations on the strength of columns as obtained by tests. When the column failure is definitely of the primary bending type it is advisable to plot the test results with nondimensional coefficients, such as are

employed in reference 2.53. The following coefficients will be adopted for this purpose:

$$R_a = \text{allowable stress ratio} = F_c / F_{co} \quad (1.6311)$$

where

$$F_c = \text{allowable column stress}$$

$$F_{co} = \text{column yield stress}$$

$$B = \text{slenderness ratio factor} = \frac{L'/\rho}{\pi \sqrt{E/F_{co}}} \quad (1.6312)$$

where

$$L' = L / \sqrt{c} \quad (\text{see equation 1.381})$$

The slenderness ratio factor can be considered as the ratio between the effective slenderness ratio ( $L'/\rho$ ) and the ( $L'/\rho$ ) at which the Euler stress for a pin-ended column would equal  $F_{co}$ .

Thus, when  $B=2$ , the Euler stress  $F_{co}$  would equal  $\frac{1}{4}F_{co}$ , or  $R_a$  would be 0.25 (since the Euler stress varies inversely as the square of  $L'/\rho$ ).

1.632 *Typical column curves.* Typical column curves plotted in terms of these nondimensional coefficients are illustrated in figure 1.632. It will be noted that the Johnson parabolic curve is tangent to the Euler curve at a value of  $R_a=0.5$ ; that is, the Euler formula will not apply when it gives stresses higher than half the column yield stress. It is also convenient to know that the stresses given by the 1.5 parabolic formula and the straight line formula are equal to those given by the Euler formula at values of  $R_a$  equal to 0.4286 and 0.333, respectively.

#### 1.64 LOCAL INSTABILITY FAILURE

1.641 *General.* Columns may fail by a local collapse of the wall at a stress below the primary failure stress. The general equation for the local failure of round tubes is given in the following

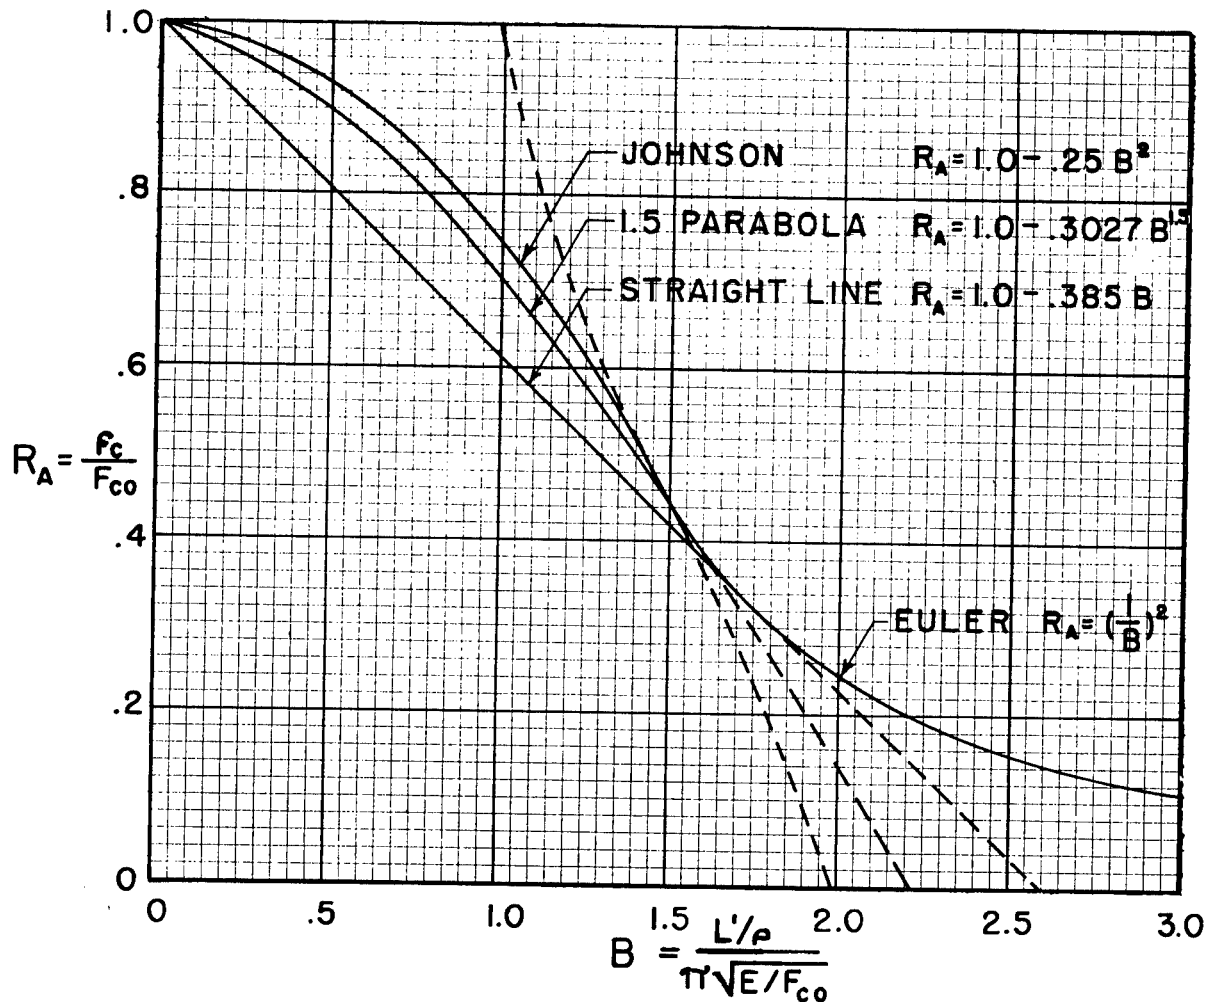


Figure 1.632. Various column curves in nondimensional form.

section. The local failure of columns having cross sections other than those of round tubes is discussed in section 1.65.

1.642 *Crushing or crippling stress ( $F_{cc}$ )*. The upper limit of the allowable column stress for local failure is called the crushing or crippling stress and is designated  $F_{cc}$ . The crushing stresses of round tubes subject to plastic failure generally can be expressed by a modified form of the equation for the buckling of a thin-walled cylinder in compression as given below:

$$F_{cc} = K \sqrt{E' E'' / D/t} \dots \dots (1.6421)$$

The effective modulus  $E'$  can be determined from the basic column curve for primary failure by the method given in section 1.623. As the value of the effective modulus corresponds to a given value of stress it usually is convenient to: (1) Assume a value of  $F_{cc}$ ; (2) compute the corresponding value of  $E'$ ; (3) substitute these values into equation 1.6421 and solve for  $D/t$ . This latter value is the  $D/t$  at which crushing will occur at the assumed stress. Values of the constant  $K$  must be determined empirically. As noted above, equation 1.6421 applies to plastic failure; i. e., for stresses above the proportional limit. In the case of thin-walled tubes which fail locally at stresses below the proportional limit, the initial eccentricities are likely to be larger relatively and the constant should be suitably reduced.

#### 1.65 COLUMNS OF UNCONVENTIONAL CROSS SECTION

1.651 *General*. In the case of columns having unconventional cross sections which are particularly subject to local instability, it is necessary to establish the curve of transition from local to primary failure. In determining the strength curves for such columns, sufficient tests should be made to cover the following points:

1.652 *Nature of "short column" curve*. The test specimens should cover a range of  $\frac{L'}{\rho}$  which will extend to the Euler range, or at least well beyond the values to be used in construction. When columns are to be attached eccentrically in the structure, some tests should be made to determine the effects of eccentricity. This is important particularly in the case of open sections, as the allowable loads may be affected considerably by the location of the point of application of the column load.

1.653 *Local failure*. When local failure occurs,

the crushing or crippling stress  $F_{cc}$  can be determined by extending the "short column" curve for the specific cross section under consideration to a point corresponding to zero  $L'/\rho$ . When a family of columns of the same general cross section is used, it is often possible to determine a relationship between  $F_{cc}$  and some factor depending on the wall thickness, width, diameter, or some combination of these dimensions. Extrapolations of such data should be avoided by covering an adequate range in the tests.

1.654 *Reduction of test results on aluminum and magnesium alloys to standard*. The use of correction factors given in figures 1.654 is considered satisfactory and is acceptable to the Air Force, Navy, and the Civil Aeronautic Administration for use in connection with tests on aluminum and magnesium alloys. (Note that an alternate method is given in par. 1.655.) In using figures 1.654, the correction of the test result to standard is made by multiplying the stress developed in a test of a column specimen by the factor  $K$ . This factor may be considered applicable regardless of the type of failure involved (i. e., column crushing or twisting). In figures 1.654,  $F_c$  is the ultimate compressive stress of the test specimen,  $F_{cy}$  is the compressive yield stress of the test specimen, and  $F_{cy}(\text{std.})$  is the standard compressive yield stress as given in Tables 3.111.

Acceptable methods for obtaining compressive yield strengths for use in determining values of  $K$  from figures 1.654 are as follows:

(a) Direct compressive stress-strain measurements of the material of which the test column is made in the direction of loading of the test column.

(b) If method (a) is not feasible, the compressive stress desired may be obtained from the tensile yield stress as follows: Determine the tensile yield stress of the column test specimen material by direct tensile stress-strain measurements in a direction parallel to the test column length. Compute the compressive yield stress along the length of the test column by multiplying the tensile yield strength by the proper ratio of the design allowable compressive yield strength to the design allowable tensile yield strength; the ratio chosen should account for the grain direction of the test column. In case the compression test column is manufactured indiscriminately with respect to material grain, the tensile test specimen should be made with the grain parallel to its length and the

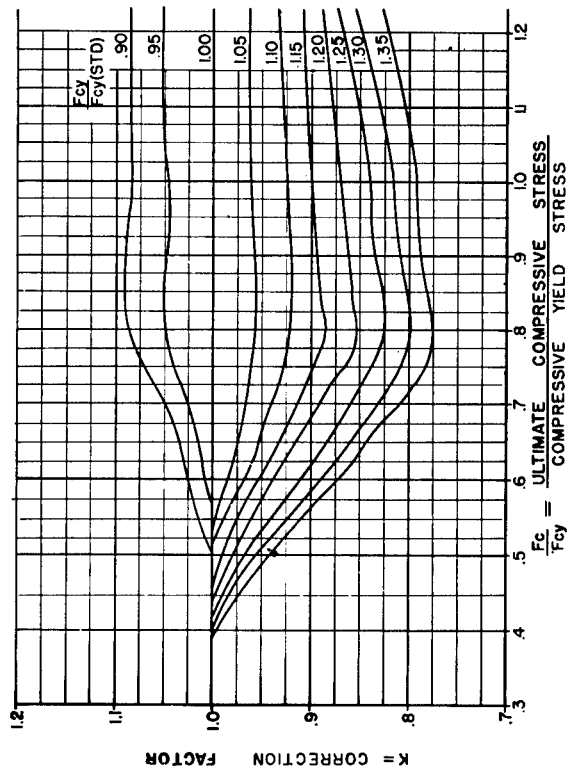
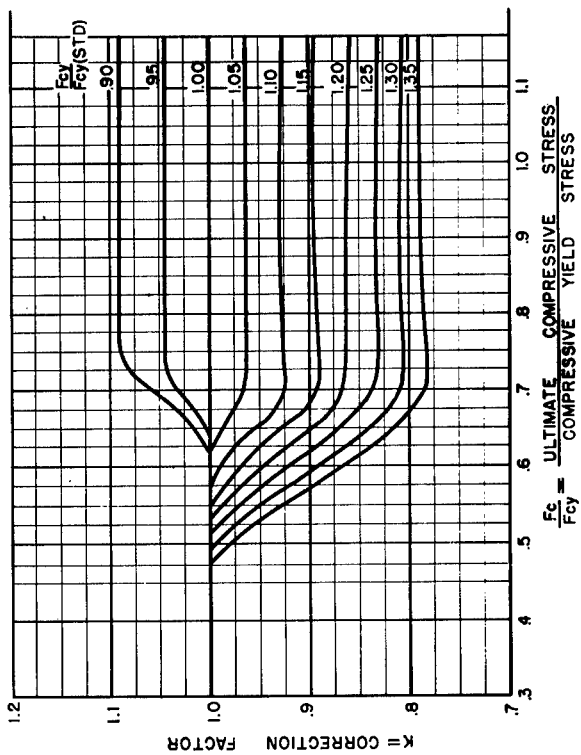


Figure 1.654 (a). Nondimensional material correction chart for 24S-T3 sheet.

Figure 1.654 (b). Nondimensional material correction chart for 24S-T3 clad sheet.

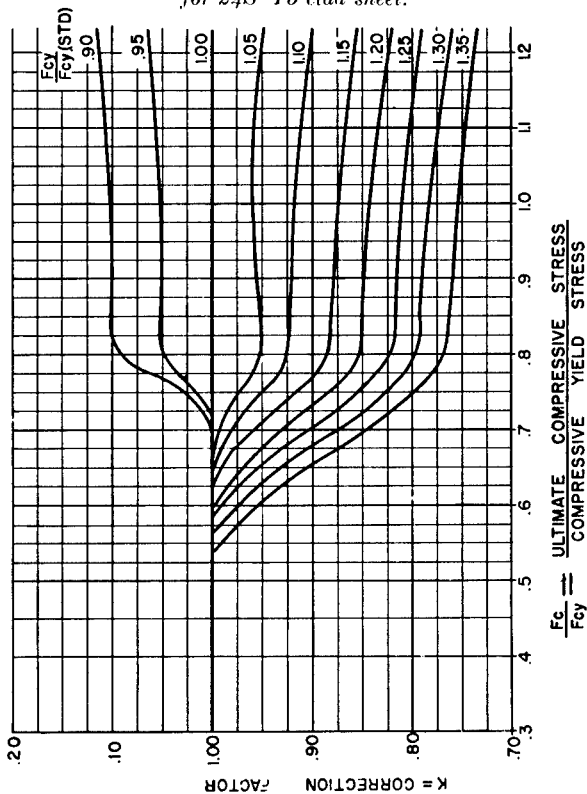
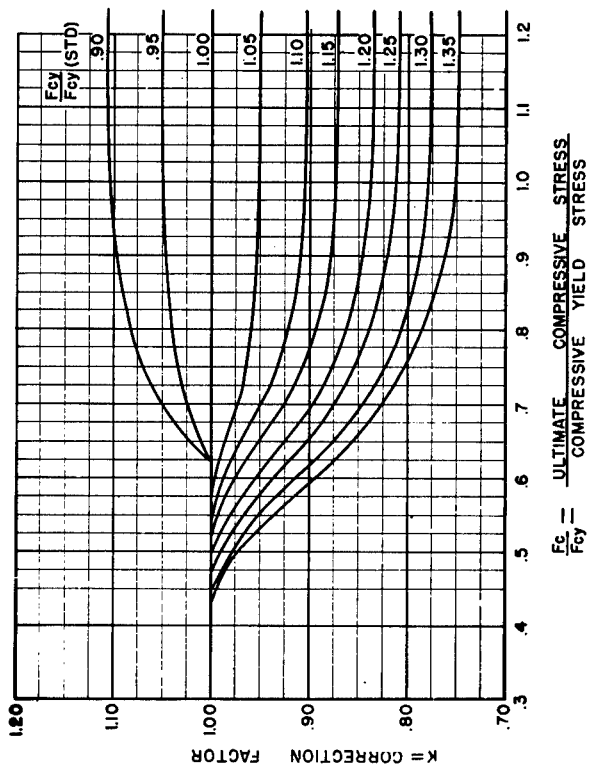


Figure 1.654 (c). Nondimensional material correction chart for 24S-T4 extrusions less than 1/4 inch thick.

Figure 1.654 (d). Nondimensional material correction chart for 24S-T4 extrusions 1/4 to 1 1/2 inches thick.

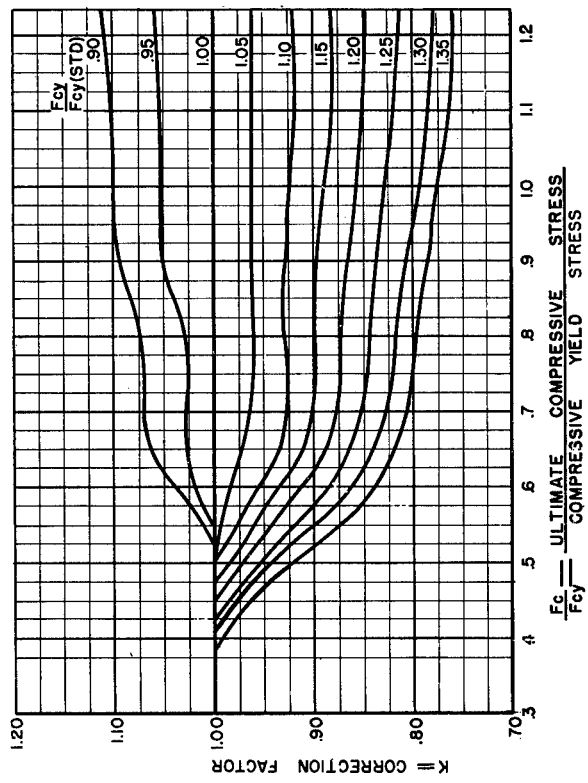


Figure 1.654 (e). Nondimensional material correction chart for 24S-T3 tubing.

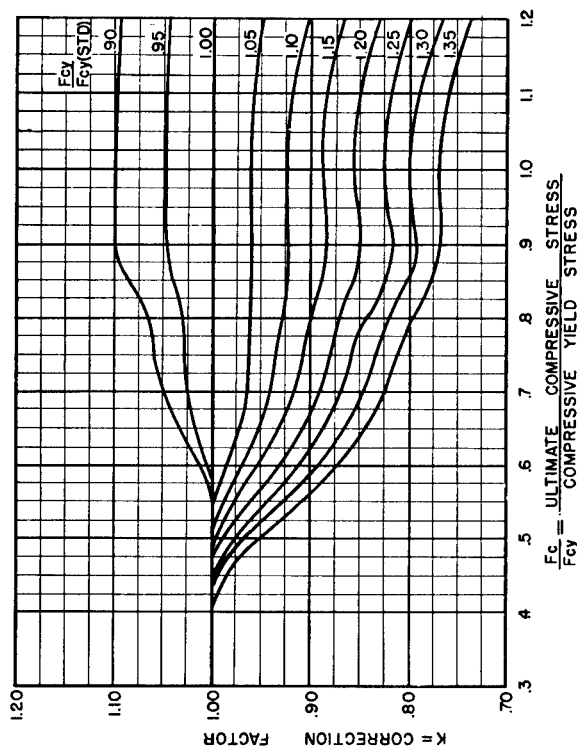


Figure 1.654 (f). Nondimensional material correction chart for 14S-T3 (R301-T3) clad sheet.



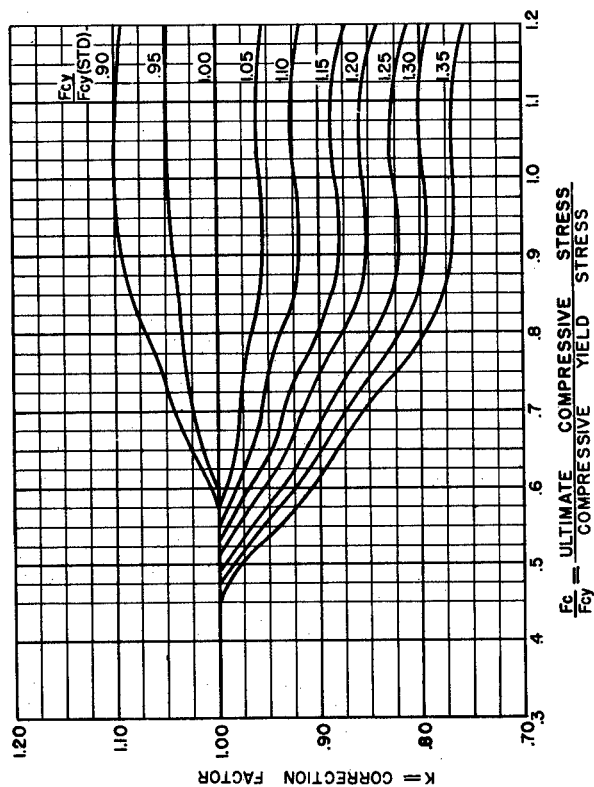


Figure 1.654 (g). Nondimensional material correction chart for 75S-T6 clad sheet.

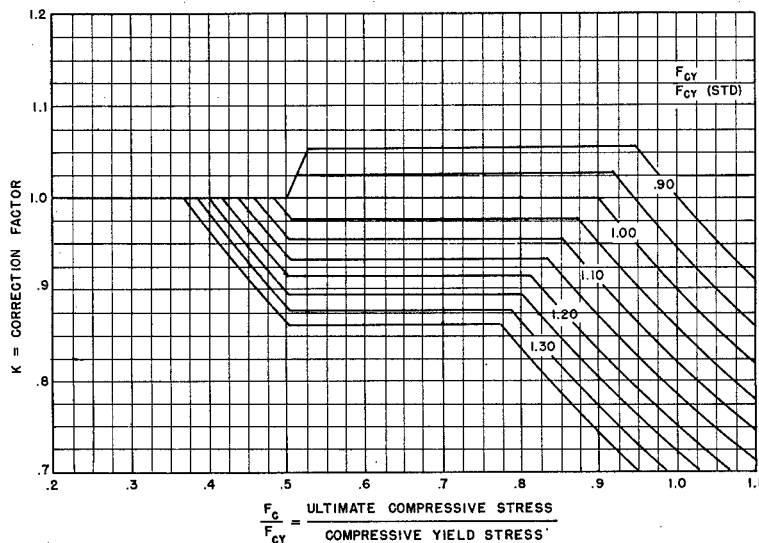


Figure 1.654 (h). Nondimensional material correction chart for M or AM 3S open extrusions.

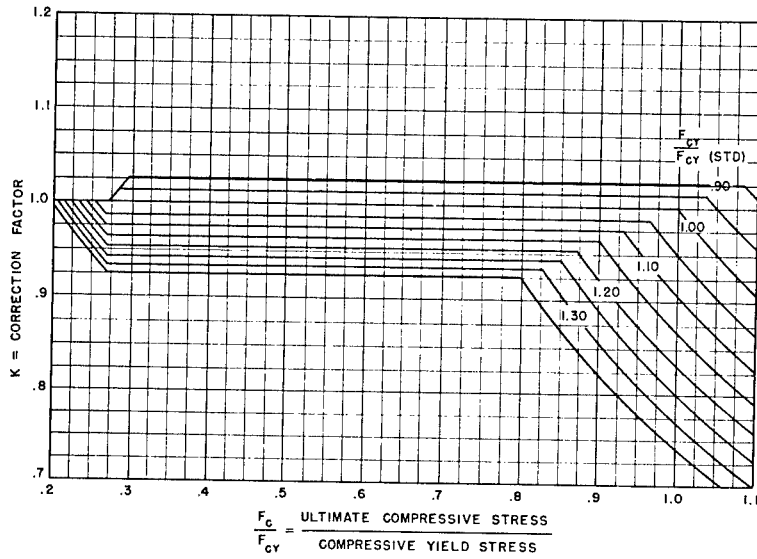


Figure 1.654 (i). Nondimensional material chart for FS-1, J-1, O-1, AM C52S, AMC 57S or AMC 58S open extrusions.

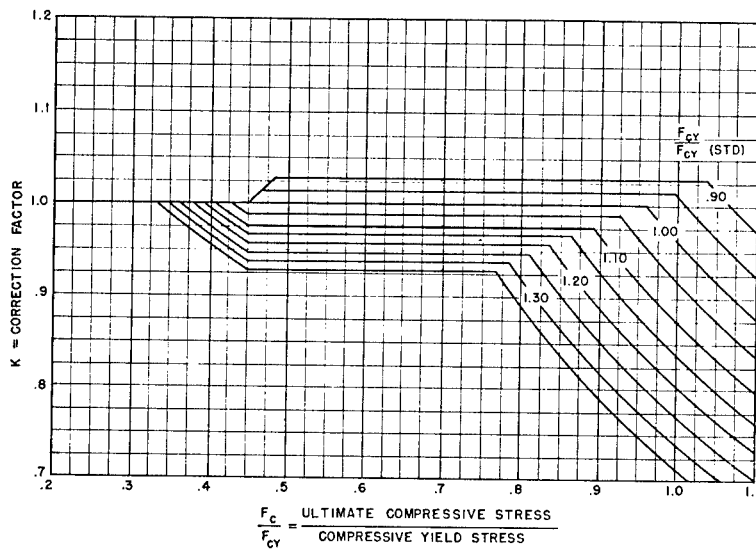


Figure 1.654 (j). Nondimensional material correction chart for AM C58S-T5 or O-1HTA open extrusions.

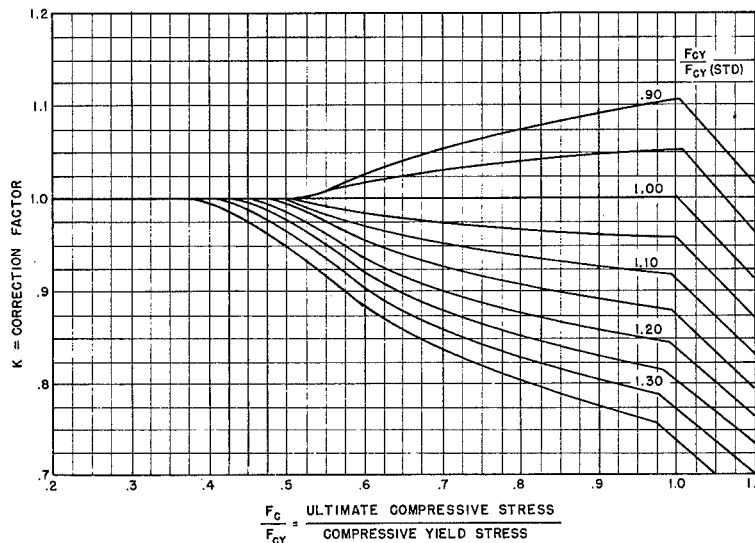


Figure 1.654 (k). Nondimensional material correction chart for FS-1h or AM C52S-H sheet.

with-the-grain ratio of the design allowable compressive yield to design allowable tensile yield strength for the material should be used.

(c) In case neither methods (a) nor (b) are feasible or applicable, it should be assumed that the compressive yield of the column test specimen parallel to its length is 15 percent greater than the minimum established design allowable yield strength for the material in the column test specimen.

1.655 *Reduction of test results to standard-alternate method.* The use of the method of reducing test results to standard illustrated in figure 1.655 is considered satisfactory and is acceptable to the Air Force, Navy, and the Civil Aeronautics Administration. This method is conservative for aluminum alloys and is considered an acceptable method for correcting test results for other materials.

The following procedure should be used to obtain the corrected test results:

(a) Determine the compressive yield strength of the material in the column test specimen by one of the methods outlined in paragraphs 1.654 (a), (b), or (c); for materials other than aluminum alloy use a method similar to one of those described in these paragraphs.

(b) Construct an Euler curve (see fig. 1.655) for the material in the column test specimen.

(c) Plot two straight lines tangent to the Euler

curve with intercepts on the compressive stress ordinate at values determined from the appropriate formula:

Aluminum alloys— $F_c = F_{cy}(1 + F_{cy}/200,000)$

Magnesium alloys— $F_c = 1.18 F_{cy}$

Steel— $F_c = F_{cy}$

One intercept is determined by substituting the compressive yield strength of the material in the appropriate formula and the other by substituting the design allowable compressive yield strength for the material in the test specimen in the formula.

(d) When the test specimen has been tested, the test value is marked on the compressive stress ordinate, a horizontal line is drawn to intersect the straight line based on the test material compressive yield strength. A vertical line is erected at this point of intersection to intersect the other straight line based on the standard compressive yield strength, and a horizontal line extended from this point of intersection back to the compressive stress ordinate thus establishing the corrected test stress value.

## 1.7 Thin-walled and stiffened thin-walled sections

1.71 GENERAL. A bibliography of information compiled by the National Advisory Committee for Aeronautics on thin-walled and stiffened thin-walled sections is contained in reference 1.71.

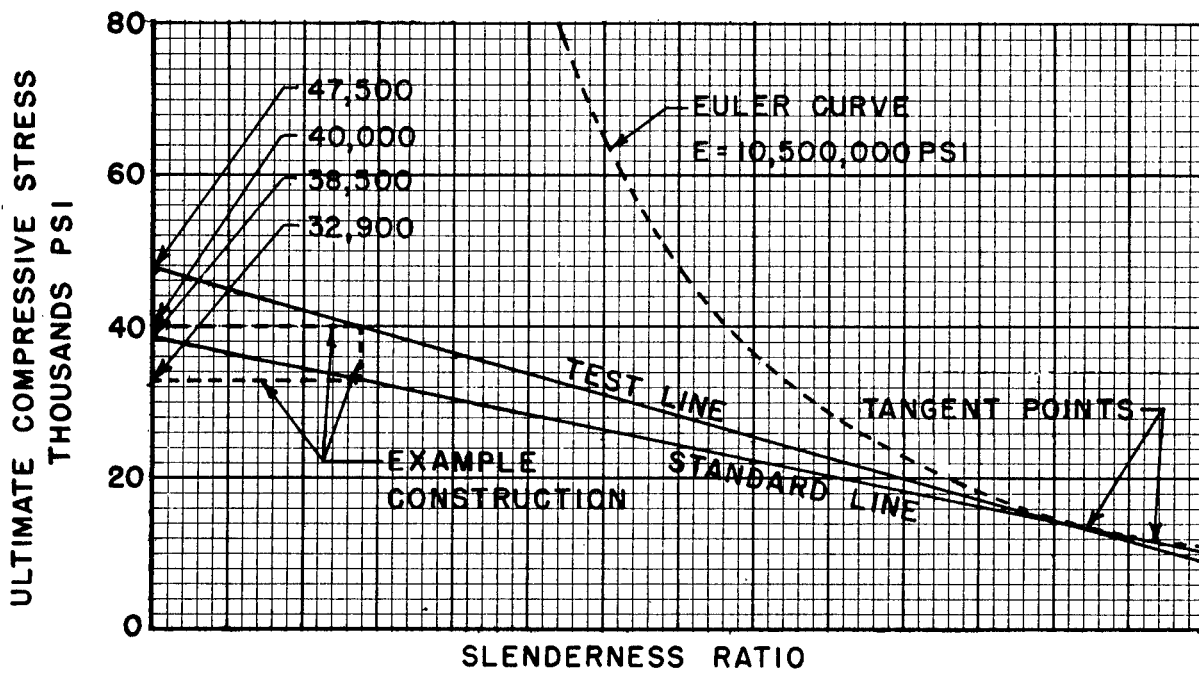


Figure 1.655. Illustrative material correction curves for columns (alternate method).

## CHAPTER 2

### STEEL

#### 2.1 General properties

##### 2.1.1 NORMAL (ROOM) TEMPERATURE PROPERTIES

2.1.1.1 *Design mechanical properties.* The gen-

eral strength properties and the related characteristics of various steels at normal (room) temperature are listed in tables 2.111. Particular attention should be paid to the detailed notes at the bottom of each table.

Table 2.111 (a). *Design Mechanical Properties<sup>a</sup> of Plain Carbon Steels (Kips Per Square Inch)*

Type.....	Tube, sheet, and bar	
Alloy.....	1020-25	
Specification.....	AN-S-11, MIL-S-7097, MIL-T-5066, and AN-WW-T-846	
Condition.....		
Diameter or thickness.....		
$F_{tu}^b$ .....	$L^c$ .....	} 55
	$T$ .....	
$F_{ty}$ .....	$L$ .....	} 36
	$T$ .....	
$F_{cy}$ .....	$L$ .....	} 36
	$T$ .....	
$F_{su}$ .....		35
$F_{brv}(e/D=1.5)^d$ .....		90
$F_{brv}(e/D=2.0)$ .....		
$F_{brv}(e/D=1.5)$ .....		
$F_{brv}(e/D=2.0)$ .....		
$E$ .....		28,000
$E_c$ .....		28,000
$G$ .....		10,000
$W$ lbs./in. <sup>3</sup> .....		0.283
Commercial designation.....		

<sup>a</sup> Where joints with tapered welds at angles of 30° or less to the center line, or fish-mouth welds formed by cuts of 60° or less are used, the allowable tensile stress near the weld can be assumed to be 50,000 p. s. i.

<sup>b</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

<sup>c</sup>  $L$ =longitudinal, parallel to direction of rolling,  $T$ =transverse, perpendicular to direction of rolling.

<sup>d</sup>  $D$ =hole diameter;  $e$ =edge distance measured from the hole center line in the direction of stressing; use value of  $e/D=2.0$  for all larger values of edge distance; for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation; values for  $e/D<1.5$  must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

Table 2.111 (b). Design Mechanical Properties of Alloy Steels \* (Kips Per Square Inch)

Type	Sheet, plate, tube, bar and rod		Plate and bar	Plate, tube, and bar	Sheet, plate, tube, bar, and rod					
Alloy	4130		Alloy steels containing less than ½ percent carbon							
Specification	AN-QQ-S-685 MIL-T-6731	MIL-T-6736 AN-S-684			Heat treated (quenched and drawn)					
Condition	N <sup>b</sup>		Annealed		HT 100 ksi	HT 125 ksi	HT 150 ksi	HT 180 ksi	HT 200 ksi <sup>c</sup>	
Diameter or thickness	t > 0.188	t < 0.188	t > 1.50	t < 1.50						
$F_{tu}$ <sup>d</sup>	L <sup>e</sup>	90	95	55	65	100	125	150	180	200
$F_{tv}$		T	70	75	36	45	80	100	135	165
$F_{cu}$	L		70	75				100	135	165
$F_{su}$	T	55	55	35	40	65	75	90	105	115
$F_{bru}$ (e/D=1.5) <sup>f</sup>										
$F_{bru}$ (e/D=2.0)		140	140	90	110	140	175	190	200	
$F_{brv}$ (e/D=1.5)										
$F_{brv}$ (e/D=2.0)										
E		29,000	29,000	29,000	29,000	29,000	29,000	29,000	29,000	29,000
E <sub>c</sub>		29,000	29,000	29,000	29,000	29,000	29,000	29,000	29,000	29,000
G		11,000	11,000	11,000	11,000	11,000	11,000	11,000	11,000	11,000
W lbs./in. <sup>3</sup>		0.283	0.283	0.283	0.283	0.283	0.283	0.283	0.283	0.283
Commercial designation		4130								

\* Except as noted, the values given in this table apply to any of the structural alloy steels containing less than ½ percent carbon. Any of these steels will display the properties given in the column corresponding to its ultimate tensile stress. These values apply to the materials in various forms, such as bars, rods, tubes, sheet, castings, forgings, etc. In the case of castings the above values correspond to those obtained from test bars. Reference should be made to the specific requirements of the procuring or certifying agency in regard to the use of the above values in the design of castings.

<sup>b</sup> This value is applicable when the material is furnished in condition N of the applicable MIL specification but the yield strength is appreciably reduced when normalized.

<sup>c</sup> The use of higher heat-treatments than that corresponding to  $F_{tu}=180,000$  p. s. i. shall be based on rulings of the procuring or licensing agencies.

<sup>d</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

<sup>e</sup> L=longitudinal, parallel to direction of rolling; T=transverse, perpendicular to direction of rolling.

<sup>f</sup> D=hole diameter; e=edge distance measured from the hole center line in the direction of stressing; use value of e/D=2.0 for all larger values of edge distance; for ratios between 1.5 and 2.0, the bearing stress should be obtained by linear interpolation; values for e/D<1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

\* Applicable only when section, size, and hardenability permit the formation of a minimum of 50 percent Martensite in the center of the section on quenching. For alloy steels heat-treated to an ultimate tensile strength of 200 ksi an allowable tensile yield strength of 175 ksi may be used provided the quenched structure at the center of the material contains not less than 90 percent Martensite and the subsequent draw temperature exceeds 700° F. For information, the maximum section sizes that permit the formation of the required Martensite in the center of the material and for which design allowable tensile yield strengths of 175 ksi at 200 ksi ultimate tensile strength and 165 ksi at 180 ksi and 200 ksi ultimate strength are permissible, are listed below.

Steel Alloy	Maximum section thickness for 165 ksi (50 percent Martensite)	Maximum section thickness for 175 ksi (90 percent Martensite)
4130, 8630	1"	½"
8735	1½"	¾"
8740	1¾"	1"
4140	2"	1"
4340	4"	3"

Table 2.111 (c). Design Mechanical Properties of Corrosion Resisting and Heat-treated, Corrosion Resisting Steels (Kips Per Square Inch)

Type.....		Sheet and strip								
		18-8								
Alloy.....		MIL-S-5059 Class I and II								
Specification.....		MIL-S-5059 Class I and II								
Condition.....		Annealed	Cold rolled				Cold rolled and heat-treated *			
			¼ hard	½ hard	¾ hard	Full hard	¼ hard	½ hard	¾ hard	Full hard
Diameter or thickness										
$F_{tu}^b$ .....	$L^c$ .....	75	125	150	175	185	125	150	175	185
	$T$ .....									
$F_{tu}^d$ .....	$L$ .....	30	75	110	135	140	75	120	140	160
	$T$ .....									
$F_{cu}$ .....	$L$ .....	35	65	85	95	105	75	105	120	140
	$T$ .....	35	100	120	140	170	105	125	160	185
$F_{au}$ .....		40	67.5	80	95	100	• 67.5	• 80	• 95	• 100
$F_{bru}(e/D=1.5)^f$ .....		75	150	180	190	195	• 150	• 180	• 190	• 195
$F_{bru}(e/D=2.0)$ .....										
$F_{brv}(e/D=1.5)$ .....										
$F_{brv}(e/D=2.0)$ .....										
$E$ .....	$L$ .....	29,000	27,000	26,000	26,000	26,000	27,000	27,000	27,000	27,000
	$T$ .....	29,000	28,000	28,000	28,000	28,000	29,000	29,000	29,000	29,000
$E_c$ .....	$L$ .....	28,000	26,000	26,000	26,000	26,000	27,000	27,000	27,000	27,000
	$T$ .....	28,000	27,000	27,000	27,000	27,000	28,000	28,000	28,000	28,000
$G$ .....		12,500	12,000	11,500	11,000	11,000	12,000	11,500	11,000	11,000
$W$ lbs./in. <sup>3</sup> .....		0.286				0.286	0.286	0.286	0.286	0.286
Commercial designation.....										

\* Heat-treatment consists of holding from 16 to 36 hours at 300°-200° C., (570°-392° F.), and cooling in air.

<sup>b</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

<sup>c</sup>  $L$ =longitudinal, parallel to direction of rolling;  $T$ =transverse, perpendicular to direction of rolling.

<sup>d</sup> The 0.2 percent offset minimum yield stresses were determined on the basis of the initial moduli of elasticity as shown by the stress-strain data.

\* These data are safely based on the "as-cold-rolled" material, and should be higher for the "cold-rolled and heat-treated" material.

<sup>f</sup>  $D$ =hole diameter;  $e$ =edge distance measured from the hole center line in the direction of stressing; use value of  $e/D=2.0$  for all larger values of edge distance, for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation, values for  $e/D<1.5$  must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

2.112 *Fatigue properties.* Rotating beam fatigue strength data for ferrous materials and reversed bending fatigue strength data for chromium — 18 percent, nickel — 8 percent, sheet material are given in tables 2.112 (a) and 2.112 (b), respectively. In using these data it should be remembered that they have been obtained from specimens in which stress concentrations are purposely minimized, and that suitable allowance should be made for re-entrant conditions which may produce localized high stresses. These localized high stresses are of great importance in studying the effect of repeated stress.

The values given in table 2.112 (a) were determined by testing 0.30 inch diameter machined specimens in R. R. Moore rotating beam fatigue machines and represent extreme fiber stresses which such specimens will withstand in completely reversed flexure. The values given in table 2.112 (b) were determined by testing cantilever sheet specimens in Krouse constant deflection type fatigue testing machines and represent extreme fiber stresses which such specimens will withstand in completely reversed flexure.

Table 2.112 (a). Rotating Beam Fatigue Data for Ferrous Materials

(All values of stress in p. s. i.)

[Values given were determined by testing 0.30 inch diameter machined specimens in R. R. Moore rotating beam fatigue machines and represent extreme fiber stresses which such specimens will withstand in completely reversed flexure]

Material	Condition	Ultimate tensile strength	Approximate maximum stresses which material will withstand for various numbers of cycles			
			100,000 cycles	1,000,000 cycles	10,000,000 cycles	20,000,000 cycles <sup>a</sup>
S. A. E. 4340 steel bar	Heat treated	188,000	100,000	82,000	82,000	82,000
S. A. E. 4340 steel forged bar <sup>b</sup>	do	150,000	96,000	80,000	76,000	76,000
S. A. E. 2330 steel bar	do	116,000	82,000	72,000	66,000	66,000
Do	do	193,000	98,000	95,000	92,000	92,000
S. A. E. 4130 steel bar	do	129,000	85,000	75,000	74,000	74,000
Do	do	152,000	97,000	86,000	84,000	84,000
Do	do	205,000	105,000	100,000	99,000	99,000

<sup>a</sup> Values given for 20,000,000 cycles are commonly known as endurance limits.<sup>b</sup> With grain flow.

Table 2.112 (b). Reversed Bending Fatigue Data for Chromium 18 Percent Nickel, 8 Percent Sheet Steel Longitudinal Direction

(All values of stress in p. s. i.)

[Values given were determined by testing cantilever sheet specimens in Krouse constant deflection type fatigue testing machines and represent extreme fiber stresses which such specimens will withstand in completely reversed flexure]

Temper	Thickness of sheet	Heat <sup>a</sup> treatment	Ultimate tensile strength	Approximate maximum stresses which material will withstand for various numbers of cycles			
				100,000 cycles	1,000,000 cycles	10,000,000 cycles	20,000,000 cycles <sup>b</sup>
Full hard	0.025	As rolled	191,700	86,000	75,000	72,000	72,000
Do	.025	At 450° F., 24 hours <sup>a</sup>	202,700	90,000	80,000	76,000	76,000
Do	.050	As rolled	200,000	94,000	91,000	88,000	88,000
Do	.050	At 450° F., 24 hours	208,000	98,000	98,000	93,000	93,000
Half hard	.025	As rolled	154,000	73,000	66,000	62,000	62,000
Do	.025	At 450° F., 24 hours	150,000	75,000	73,000	64,000	64,000

<sup>a</sup> "450° F., 24 hours" is an aging treatment.<sup>b</sup> Values given for 20,000,000 cycles are commonly known as endurance limits.

2.113 *Typical stress-strain and tangent modulus data.* Typical tangent modulus versus tensile stress curves for corrosion-resisting and heat-treated corrosion resisting steel sheet and strip are given in figure 2.113 for general information.

## 2.12 TEMPERATURE EFFECTS

## 2.13 CRITERIA FOR DESIGN MECHANICAL MATERIAL PROPERTIES

## 2.2 Columns

2.21 PRIMARY FAILURE. The general formulas for primary instability are given in section 1.38. For convenience, these formulas are repeated in table 2.21 in simplified form applicable to round steel tubes. These formulas also can be used for columns having cross sections other than those of round tubes when local instability is not critical.

2.22 LOCAL FAILURE. Table 2.21 also contains notes concerning the local instability of round

tubes. The local failure stresses for columns having cross sections of other shapes are given in the allowable stress curves of this chapter.



2.221 *Effects of welding.* The primary failure stress of a column having welded ends can be determined from the formulas of table 2.21 without regard for the effects of welding. These stresses, however, should not exceed a "cut-off" stress which accounts for the effects of welding on the local failure of the column. See section 2.612 for the effects of welding.

2.23 COLUMN STRESS CURVES. Curves of the allowable column stresses for various types of steel tubing are given in figures 2.23. The allowable stress is plotted against the effective slenderness ratio which is defined by the formula:

$$\frac{L'}{\rho} = \frac{L}{\rho \sqrt{c}} \quad (2.231)$$





CHAPTER 2—STEEL

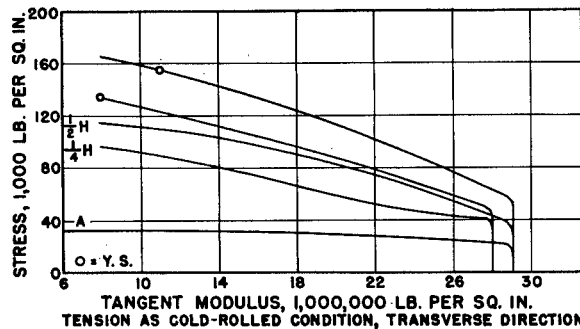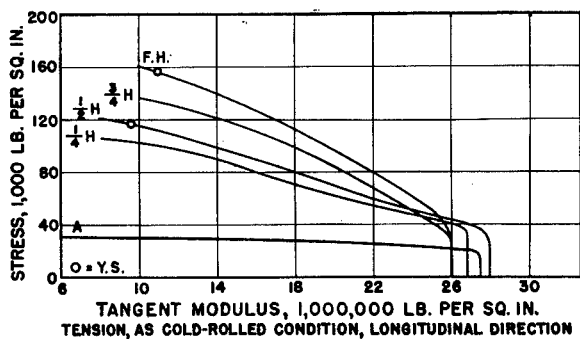



NOTES: (1) SEE SECTION 1.442 FOR EXPLANATION OF TANGENT MODULUS.  
 (2) THESE CURVES ARE BASED ON RELATIVELY FEW TESTS AND ARE THEREFORE SUBJECT TO MODIFICATION AS FURTHER DATA BECOMES AVAILABLE. WHERE THE VALUE OF INITIAL MODULUS INDICATED BY THE CURVES DIFFERS FROM THAT GIVEN IN THE TABLES, THE TABLE VALUES SHALL BE USED.

FIGURE No. 2.113 (a)

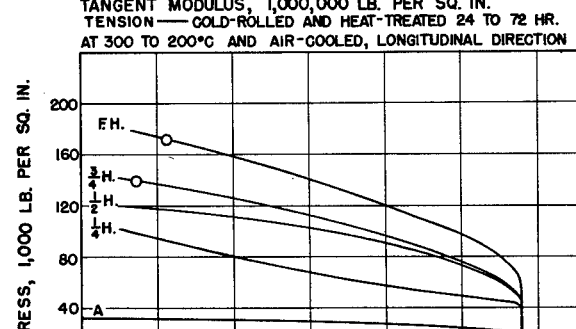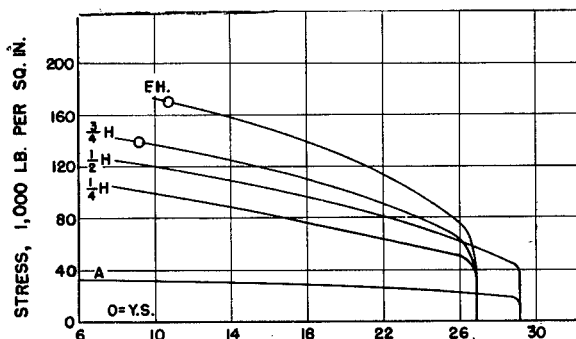



NOTES (1) AND (2), FIG. 2.113 (A), APPLY TO THIS FIGURE

FIGURE No. 2.113 (c)

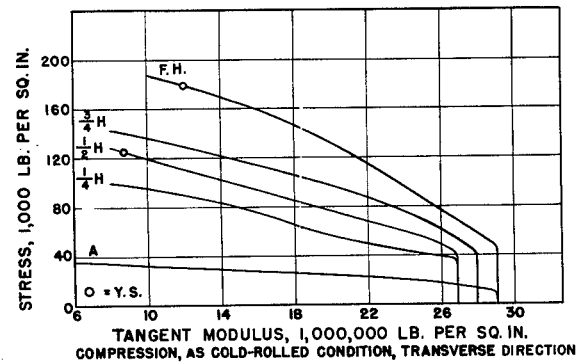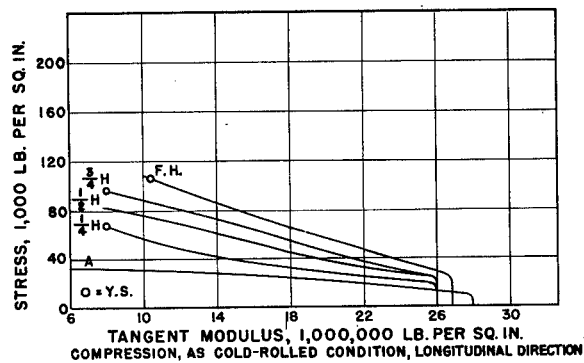

NOTES (1) AND (2), FIG. 2.113 (A), APPLY TO THIS FIGURE.

FIGURE No. 2.113 (b)

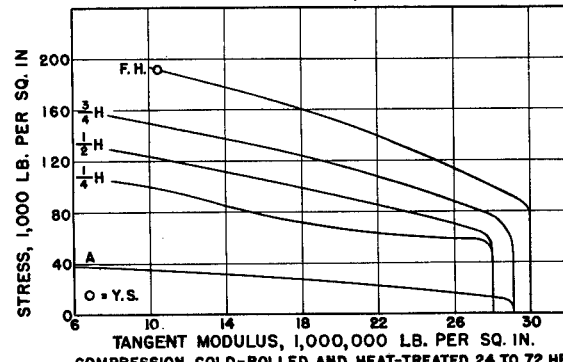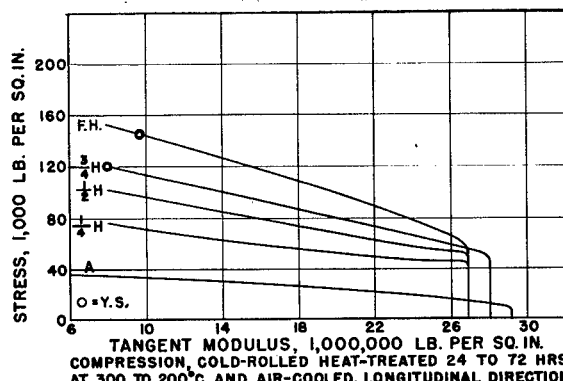

NOTES (1) AND (2), FIG. 2.113 (A), APPLY TO THIS FIGURE.

FIGURE No. 2.113 (d)

Figure 2.113. Tangent modulus curves derived from stress-strain curves for corrosion-resisting (stainless) steel sheet and plate.

Table 2.21. Column Formulas for Round Steel Tubes

Material	$F_{ty}$ -ksi	$F_{co}$ -ksi	Short columns		Critical $L'/\rho$	Long columns <sup>a</sup>	Local failure
			Column formula <sup>a</sup>	Basic equation			
1025-----	36	36	36,000—1.172 $(L'/\rho)^2$	1:383	124	$276 \times 10^6 / (L'/\rho)^2$	(c)
4130-----	<sup>d</sup> 75	79.5	79,500—51.9 $(L'/\rho)^{1.5}$	1:384	91.5	$286 \times 10^6 / (L'/\rho)^2$	(c)
Heat-treated <sup>d</sup> alloy steel---	<sup>e</sup> 100	100	100,000—8.74 $(L'/\rho)^2$	1:383	75.6	$286 \times 10^6 / (L'/\rho)^2$	(c)
Heat-treated <sup>e</sup> alloy steel---	135	135	135,000—15.92 $(L'/\rho)^2$	1:383	65.0	$286 \times 10^6 / (L'/\rho)^2$	(c)
Heat-treated <sup>e</sup> alloy steel---	165	165	165,000—23.78 $(L'/\rho)^2$	1:383	58.9	$286 \times 10^6 / (L'/\rho)^2$	(c)

<sup>a</sup>  $L'/\rho = L/\rho\sqrt{c}$ ;  $L'/\rho$  shall not exceed 150 without specific authority from the procuring or certifying agency.

<sup>b</sup> Critical  $L'/\rho$  is that above which columns are "long" and below which they are "short."

<sup>c</sup> Not necessary to investigate for local instability when  $D/t < 50$ .

<sup>d</sup> This value is applicable when the material is furnished in condition N (MIL-T-6736) but the yield strength is reduced when normalized subsequent to welding to 60,000 p. s. i.

<sup>e</sup> See "Mechanical properties," tables 2.111.

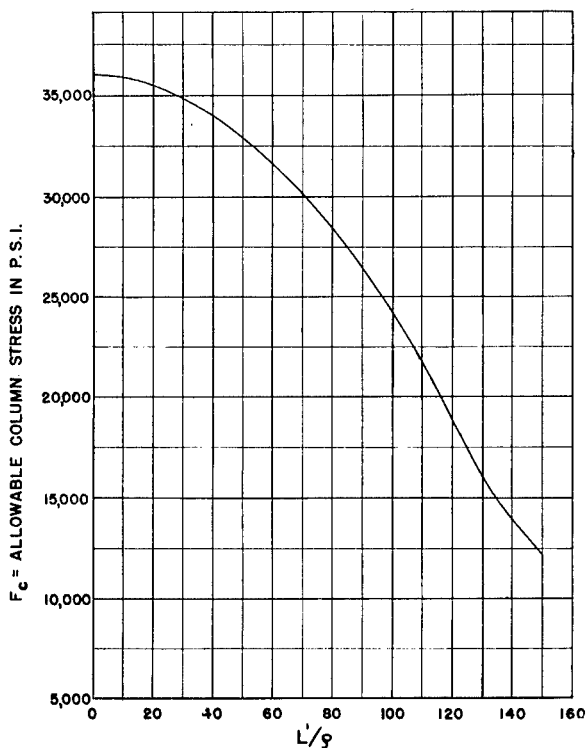


Figure 2.23 (a). Allowable column stress for 1025 steel round tubing.

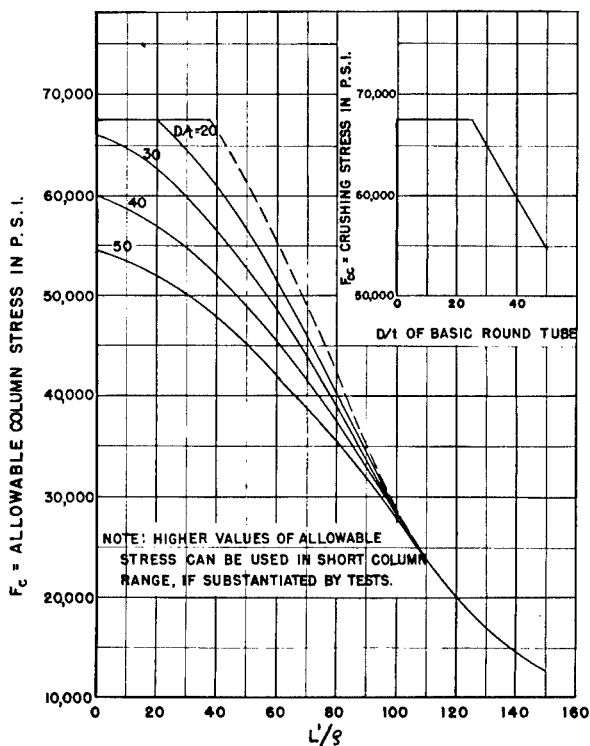


Figure 2.23 (b). Allowable column and crushing stresses for chrome molybdenum streamline tubing  $F_{ty} = 75,000$  p. s. i.

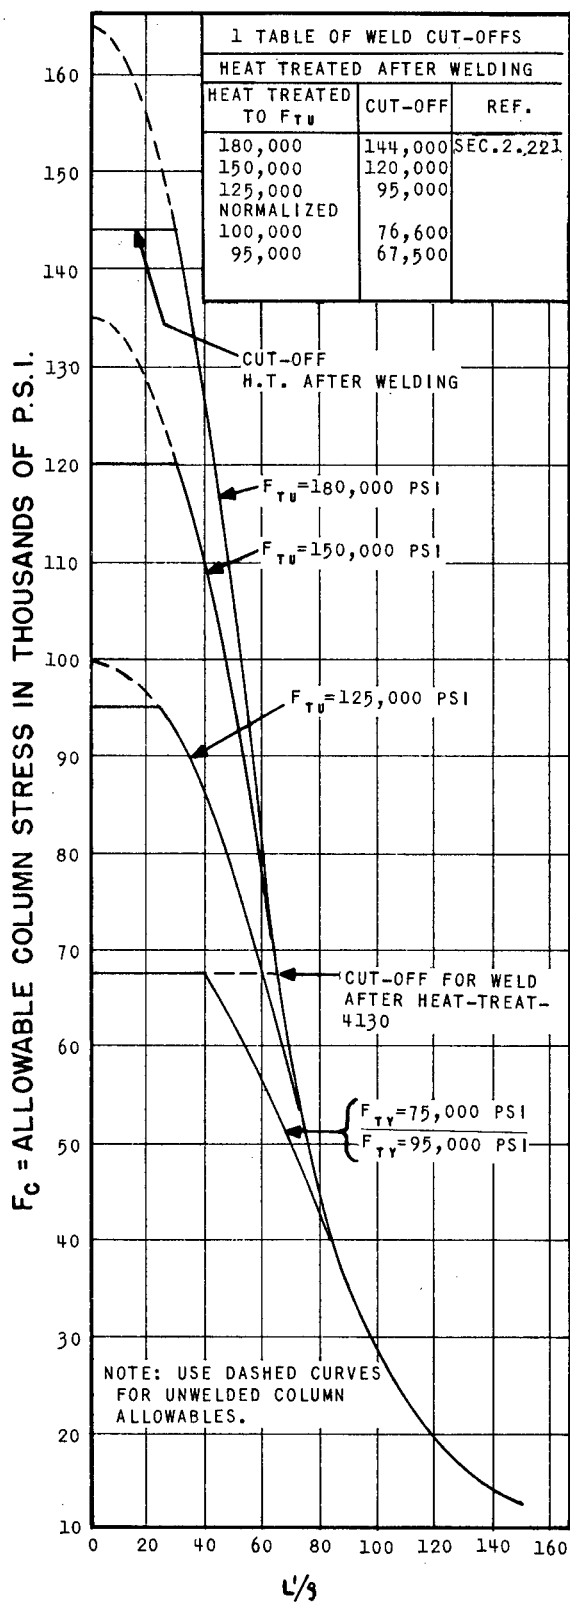


Figure 2.23 (c). Allowable column stress for heat-treated alloy steel round tubing.

2.24 COLUMN LOAD CURVES. The allowable column loads on round tubes versus length as given in reference 2.24 are satisfactory for general use and replace those curves formerly appearing in this document.

### 2.3 Beams

2.31 GENERAL. See equation 1.323; section 1.525; and reference 1.71 for general information on stress analysis of beams.

2.32 SIMPLE BEAMS. Beams of solid, tubular, or similar cross sections can be assumed to fail through exceeding an allowable modulus of rupture in bending ( $F_b$ ). For solid sections, it usually can be assumed that  $F_b$  equals the ultimate tensile stress. This assumption is conservative and higher values may be used if substantiated by test data.

2.321 Round tubes. For round tubes, the value of  $F_b$  will depend on the  $D/t$  ratio, as well as the ultimate tensile stress. Figure 2.321 gives the bending modulus of rupture for chrome molybdenum steel tubing.

2.322 Unconventional cross sections. Sections other than solid or tubular should be tested to determine the allowable bending stress.

2.33 BUILT-UP BEAMS. Built-up beams usually will fail due to local failures of the component parts. In welded steel tube beams, the allowable tensile stresses should be reduced properly for the effects of welding.

2.34 THIN-WEB BEAMS. The allowable stresses for thin-web beams will depend on the nature of the failure and are determined from the allowable stresses of the web in tension and of the flanges and stiffeners in compression.

### 2.4 Torsion

2.41 GENERAL. The torsion failure of steel tubes may be due to plastic failure of the metal, elastic instability of the walls, or to an intermediate condition. Pure shear failure usually will not occur within the range of wall thicknesses commonly used for aircraft tubing.

2.42 ALLOWABLE TORSIONAL SHEAR STRESSES. In the range of low value of  $\frac{D}{t}$ , no theoretical formula is applicable directly. The results of tests have been used to determine the empirical curves of figure 2.42.

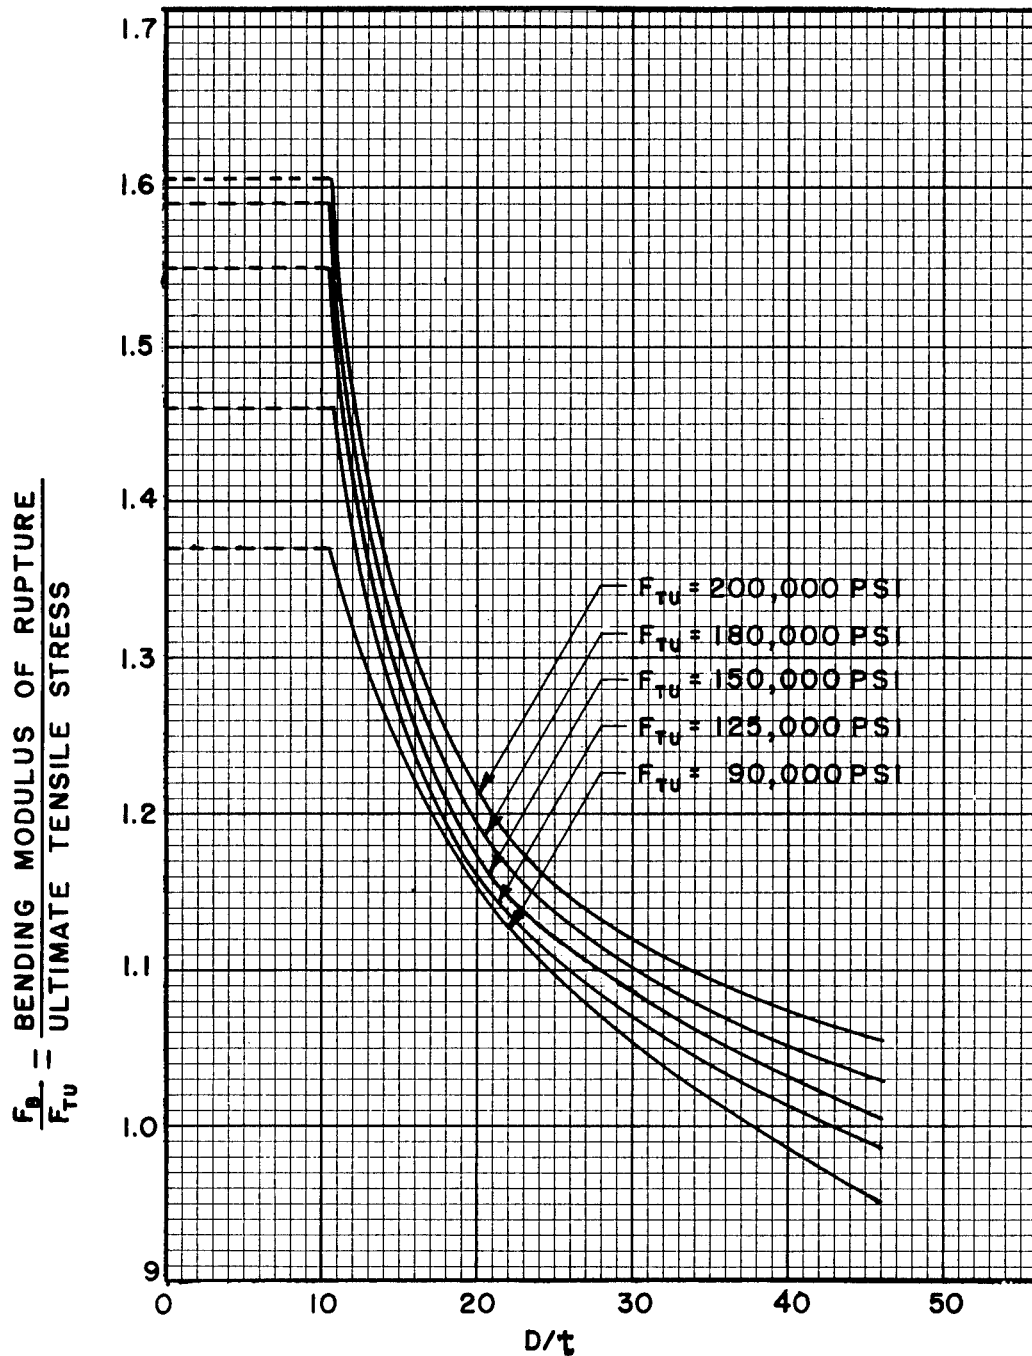


Figure 2.321. Bending modulus of rupture—chrome molybdenum steel tubing.

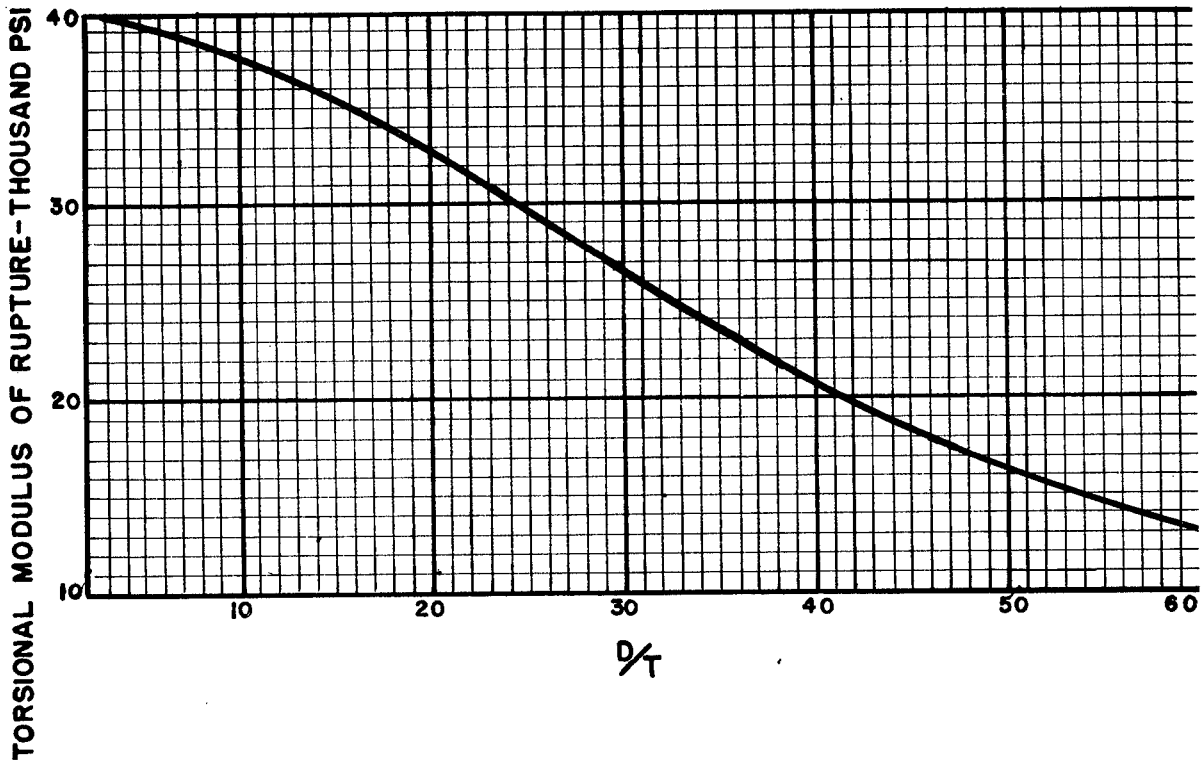


Figure 2.42 (a). Torsional modulus of rupture of 1025 steel round tubing.

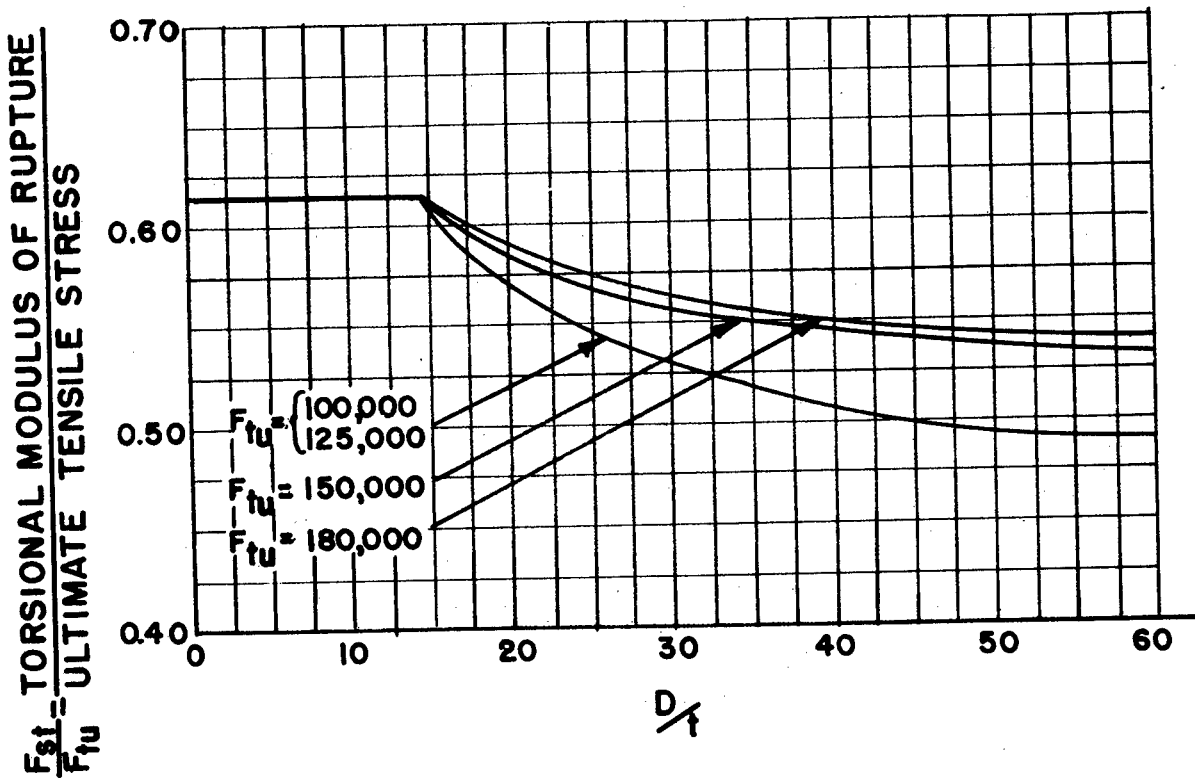


Figure 2.42 (b). Torsional modulus of rupture of round alloy steel tubing.

## 2.5 Combined loadings

2.51 ROUND TUBES IN BENDING AND COMPRESSION. The general theory of failure under combined loadings is given in section 1.535. In the case of combined bending and compression it is necessary to consider the effects of secondary bending; that is, bending produced by the axial load acting in conjunction with the lateral deflection of the column. In general, equation 1.5353, can be used in the following form for safe values:

$$\frac{f'_b}{F_b} + \frac{f_c}{F_{cv}} = 1.0 \dots \dots \dots (2.511)$$

$$\text{M. S.} = \frac{1}{R_b + R_c} - 1 \dots \dots \dots (2.511a)$$

Where

$f'_b$  = Maximum bending stress including effects of secondary bending.

$F_b$  = Bending modulus of rupture.

$f_c$  = Axial compressive stress.

$F_{cv}$  = Compressive yield stress.

In no case shall the axial compressive stress,  $f_c$ , exceed the allowable,  $F_c$ , for a simple column.

2.52 TUBES IN BENDING AND TORSION. Equation 1.5353, can be used in the following forms for safe values:

$$\left(\frac{f_b}{F_b}\right)^2 + \left(\frac{f_s}{F_{st}}\right)^2 = 1.0 \dots \dots \dots (2.521)$$

Round tubes:  $R_b^2 + R_s^2 = 1.0 \dots \dots \dots (2.521a)$

$$\text{M. S.} = \frac{1}{\sqrt{(R_b)^2 + (R_s)^2}} - 1 \dots \dots \dots (2.521b)$$

Streamline tubes:  $R_b + R_s = 1.0 \dots \dots \dots (2.522)$

$$\text{M. S.} = \frac{1}{R_b + R_s} - 1 \dots \dots \dots (2.522a)$$

$f_s$  = Shear stress.

$F_{st}$  = Torsional modulus of rupture.

Higher values can be used if substantiated by adequate test data.

2.53 TUBES IN BENDING COMPRESSION, AND TORSION. The bending stresses should include

Table 2.6111 (a). Shear and Tensile Strengths, Areas, and Moments of Inertia of Steel Bolts and Pins

Material.....					Low-carbon steel	Heat-treated steel		
Tensile strength, kips per square inch.....					55	100	125	125
Shear strength, kips per square inch.....					35	65	75	75
AN standard bolt designation	Size of bolt or pin	Machine screw size (No.)	Area of solid section (square inch)	Moment of inertia of solid (in <sup>4</sup> )	Allowable single shear strength (pounds)			Tension (pounds) (in thread)
	1/16		0.003068	0.00000075	107	199	230	
	3/32		.006902	.00000379	242	449	518	
	0.112	4	.009852	.00000772	345	640	739	
	1/8		.012272	.00001198	430	798	920	
	0.138	6	.014957	.00001781	523	972	1,122	
	5/32		.01918	.00002926	671	1,247	1,438	
	0.164	8	.02112	.00003549	739	1,372	1,584	
AN-3	3/16		.02761	.00006066	966	1,794	2,070	
	0.190	10	.02835	.00006399	992	1,842	2,126	2,210
	0.216	12	.03664	.0001069	1,282	2,381	2,748	
	7/32		.03758	.0001125	1,315	2,442	2,818	
AN-4	1/4		.04908	.0001918	1,717	3,190	3,680	4,080
AN-5	5/16		.07669	.0004682	2,684	4,984	5,750	6,500
AN-6	3/8		.1105	.0009710	3,868	7,183	8,280	10,100
AN-7	7/16		.1503	.001797	5,261	9,770	11,250	13,600
AN-8	1/2		.1963	.003069	6,871	12,760	14,700	18,500
AN-9	5/8		.2485	.004914	8,697	16,152	18,700	23,600
AN-10	3/4		.3068	.007492	10,738	19,942	23,000	30,100
AN-12	7/8		.4418	.01553	15,463	28,717	33,150	44,000
AN-14	1		.6013	.02878	21,046	39,085	45,050	60,000
AN-16	1 1/8		.7854	.04908	27,489	51,051	58,900	80,700
AN-18	1 1/4						73,750	101,800
AN-20							91,050	130,200

the effects of secondary bending due to compression. The following empirical equation will serve as a working basis, pending a more thorough investigation of the subject.

$$\left(\frac{f_b'}{F_b}\right)^2 + \left(\frac{f_s}{F_{st}}\right)^2 = \left(1 - \frac{f_c}{F_{cu}}\right)^2 \quad (2.531)$$

$$M. S. = \frac{1}{R_c + \sqrt{(R_b)^2 + (R_s)^2}} - 1 \quad (2.531.a)$$

In no case shall the axial compressive stress,  $f_c$ , exceed the allowable stress,  $F_c$ , for a simple column.

## 2.6 Joints, parts and fittings

### 2.61 JOINTS

#### 2.611 Riveted and bolted joints

2.6111 Allowable shear and tension stresses for bolts and pins. The allowable shear stress for bolts and pins is given in table 2.6111 (a). The allowable tension stress for AN bolts as well as allowable design loads are also given therein. (Interaction curves for combined shear and tension loading on AN bolts are given on fig. 2.6111.) Shear and tension allowable for NAS internal wrenching bolts are specified in table 2.6111 (b).

#### 2.6112 Allowable bearing stresses

2.61121 Joints having no motion. The basic values of the allowable stresses for various steels may be found in tables 2.111. These stresses are applicable only when the  $D/t$  ratio (diameter of rivet over thickness of sheet) is less than 5.5. When this ratio is equal to or greater than 5.5, the allowable bearing strengths must be substantiated by tests covering both yield and ultimate strengths

Table 2.6111 (b). Shear and tension strengths of internal wrenching bolts

Material.....		Heat-treated alloy steel (160,000-180,000 p. s. i.)	
Specification.....		AN-QQ-S-687 and MIL-S-6049	AN-QQ-S-690 and MIL-S-5000
Size	Standard	Ultimate tensile strength (minimum pounds)	Double shear strength (minimum pounds)
1/4	NAS 144	5,000	9,300
5/16	NAS 145	8,200	14,600
3/8	NAS 146	12,700	21,000
7/16	NAS 147	17,100	28,600
1/2	NAS 148	23,400	37,300
5/8	NAS 149	29,800	47,200
3/4	NAS 150	38,000	58,300
7/8	NAS 152	55,600	83,900
1	NAS 154	76,200	114,200
1 1/8	NAS 156	102,500	149,200
1 1/4	NAS 158	128,800	188,900
1 1/2	NAS 172	162,600	233,200
1 3/4	NAS 174	200,300	282,100
2	NAS 176	241,200	335,800

#### NOTES

Navy contractors must obtain approval of structural applications involving internal wrenching bolts prior to their use in design.

Internal wrenching nuts or equivalent should be used in applications dependent upon to develop the tabulated tensile loads.

of the joint. The unit bearing strength of steel sheets on bolts and pins is given in table 2.61121. Unit bearing strength on steel rivets may be obtained from table 3.6111 (d). These values are to be used only for the design of the connecting elements of rigid joints when there is no possibility of relative movement between the parts joined without deformation of these parts.

Table 2.61121. Unit Bearing Strengths of Sheets on Bolts and Pins ( $F_{br}=100,000$  p. s. i.) (Pounds)

Size of rivets.....	1/16	3/32	1/8	5/32	3/16	1/4	5/16	3/8	1/2	5/8	3/4	7/8	1
Plate sizes	Bearing strength of plate												
0.028	175	263	350										
0.035	219	328	438	547	656								
0.049	306	459	612	766	919	1,225							
0.058	362	544	725	906	1,087	1,450	1,812						
0.065	406	609	812	1,016	1,219	1,625	2,031						
0.072	450	675	900	1,125	1,350	1,800	2,250	2,700					
0.083	519	778	1,038	1,297	1,556	2,075	2,594	3,112					
0.095	594	891	1,188	1,484	1,781	2,375	2,969	3,563	4,750				
0.120	750	1,125	1,500	1,875	2,250	3,000	3,750	4,500	6,000	7,500			
3/16	1,172	1,758	2,344	2,930	3,516	4,688	5,859	7,031	9,375	11,719	14,063	16,406	18,750
1/4	1,563	2,344	3,125	3,906	4,688	6,250	7,813	9,375	12,500	15,625	18,750	21,875	25,000

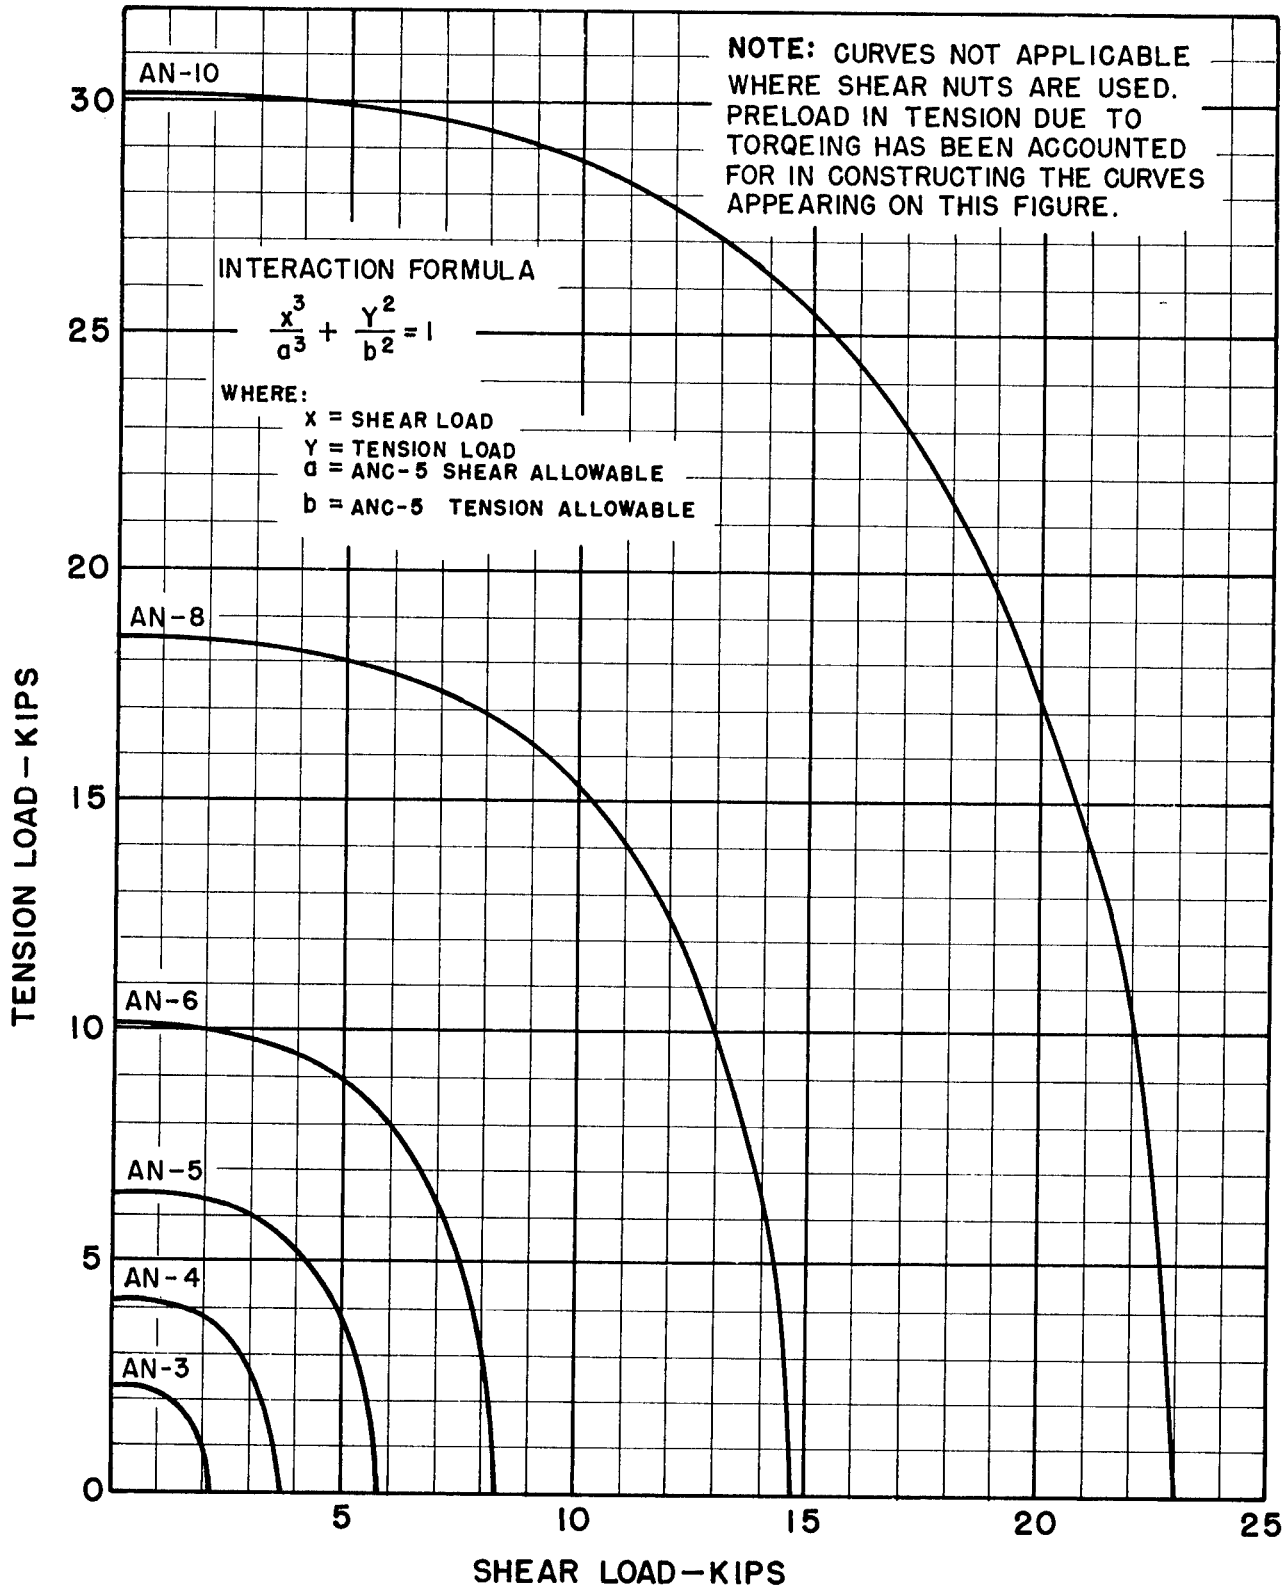


Figure 2.6111. Combined shear and tension on AN steel bolts.



Table 2.61122 (b). *Ultimate Bearing Stress for Plain Lubricated Bearings Having Frequent Relative Motion*

Type of bearing	Shock or vibration	Lubrication	Pounds per square inch
Free fits, frequent relative movement approximately 100 revolutions per hour (or equivalent) per flight.	None	Grease	15,000
Free fits, subject to very frequent relative movement, with 3 or more bearings in line, sealed or protected.	do	do	12,000
Free fits, subject to very frequent relative movement, with 3 or more bearings in line, unprotected from dirt.	do	Light grease	8,000
Free fits, subject to very frequent relative movement, with 3 or more bearings in line, unprotected from dirt.	Yes	Oil	1,500

Table 2.61122 (a).<sup>1</sup> *Bearing Factors for Plain<sup>2</sup> Bearings<sup>3</sup> Having no or Infrequent<sup>4</sup> Relative Rotation Under Design Loads*

Infrequent relative rotation under design loads	Shock <sup>4</sup> or vibration	Factor <sup>4</sup>
None <sup>7</sup>	None	1.0
Yes	do	2.0
None <sup>7</sup>	Yes	2.0
Yes	do	2.5

<sup>1</sup> The factors given in this table are applicable to other materials as well as to steel.

<sup>2</sup> Plain bearings as against antifriction bearings (ball bearings, etc.).

<sup>3</sup> Bearings are distinguished from fittings, in general, in that a bearing is a pin-jointed fitting which permits relative movement between the parts joined other than that due to deformation of the parts under load.

<sup>4</sup> Infrequent rotation is considered to be rotation of less than 100 revolutions per hour. For rotations in the order of 100 revolutions per hour, and up, see table 2.61122 (b).

<sup>5</sup> Shock is considered to occur in such structures as landing gears, gun mounts, hoisting, towing and mooring connections.

<sup>6</sup> It should be noted that the fitting factors specified by the procuring or certifying agency also apply to the bearing surfaces. If the applicable fitting factor exceeds the bearing factor, the former shall be used in lieu of (not in addition to) the latter, and vice versa.

<sup>7</sup> No relative rotation under design loads; to illustrate, some landing gear joints have no relative rotation under landing loads, although they have relative rotation during retraction.

2.61122 *Joints having motion.* For joints having motion the allowable bearing stresses for the various steels to be found in tables 2.111 are to be reduced by dividing by the factors of safety specified in table 2.61122 (a) (designated as "bearing factors"), or are to be used in accordance with table 2.61122 (b).

2.6113. *Hollow-end rivets.* If hollow-end rivets with solid cross sections for a portion of the length (AN 450) are used, the strength of these rivets may be taken equal to the strength of solid rivets of the same material, provided that the bottom of the cavity is at least 25 percent of the rivet diameter from the plane of shear, as measured toward the hollow end, and further provided that they are

used in locations where they will not be subjected to appreciable tensile stresses.

2.6114 *High shear rivets.* The allowable shear load for "Hi-Shear" rivets (NAS-177, 178, and 179) is the same as that specified for the standard aircraft bolts heat-treated to 125,000 p. s. i. and given in table 2.6111 (a). Allowable single shear strengths for annealed 18-8 steel rivets are given in table 2.6114.

Table 2.6114.<sup>1</sup> *Allowable Ultimate Single Shear Strengths 18-8<sup>2</sup> Corrosion Resistant Steel Rivets (Pounds)*

Diameter	Load
1/8	973
3/16	2150
1/4	3880
5/16	6140
3/8	8800

<sup>1</sup> Material as described in Specification AN-S-771 annealed before driving.

<sup>2</sup> The values given in the table above were computed using an allowable shear stress of 75,000 p. s. i. and nominal hole sizes from table 3.6111 (c)

2.6115 *Blind rivets.* Table 2.6115 contains ultimate and yield allowable single shear strengths for protruding and flush-head monel blind rivets in corrosion-resistant sheet. These strengths are applicable only when the grip lengths and rivet-hole tolerances are as recommended by the rivet manufacturer.

The strength values were established from test data obtained from tests of specimens having edge distances  $e/D$  equal to or greater than 2.0. Where  $e/D$  values less than 2.0 are used, tests to substantiate yield and ultimate strengths must be made. Ultimate strength values of protruding and flush blind rivets were obtained from the average failing load of test specimens divided by 1.15. Yield strength values were obtained from average yield load test data wherein the yield load is defined as the load at which the following permanent set across the joint is developed:

(a) 0.005 inches up to and including  $\frac{3}{16}$  inch diameter rivets.

(b) 2.5 percent of the rivet diameter for rivet sizes larger than  $\frac{3}{16}$  inch diameter.

Blind rivets should not be used in applications where appreciable tensile loads on the rivets will exist. Reference should be made to the requirements of the applicable procuring or certifying agency relative to the use of blind rivets.

2.6116 *Lockbolts*. Allowable loads for lockbolts are given in section 3.6116.

2.612 *Welded joints*. Whenever possible, joints to be welded should be so designed that the welds will be loaded in shear.

2.6121 *Fusion welds.—arc and gas*. In the design of welded joints the strength of both the weld metal and the adjacent parent metal must be considered. The allowable strength for the adjacent parent metal is given in paragraph 2.6122 and the allowable strength for the weld metal is given in paragraph 2.6123. The weld metal

Table 2.6115. *Ultimate and Yield Strengths for Blind Monel Cherry Rivets in Corrosion Resistant Sheet (Pounds)*

ULTIMATE STRENGTHS

Installation.....	Protruding head				100° double dimpled <sup>1</sup>			100° machine countersunk <sup>2</sup>			
	CR563										
Rivet type.....	CR562										
Sheet material.....	18-8 (½ Hard)										
$t^3$ \ D	$\frac{3}{16}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{3}{16}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{5}{32}$	$\frac{3}{16}$	
0.008.....	150	180	220	-----	280	315	-----	-----	-----	-----	
0.012.....	230	300	350	-----	320	455	*610	-----	-----	-----	
0.020.....	380	510	600	-----	400	620	680	-----	-----	-----	
0.025.....	460	620	750	1, 090	450	705	830	-----	-----	-----	
0.032.....	550	770	960	1, 380	510	810	980	*420	-----	-----	
0.040.....	620	900	1, 160	1, 660	570	900	1, 135	*420	*535	-----	
0.051.....	660	1, 000	1, 340	1, 960	-----	-----	-----	510	550	-----	
0.064.....	680	1, 090	1, 460	2, 190	-----	-----	-----	620	735	-----	
0.072.....	700	1, 140	1, 500	2, 270	-----	-----	-----	625	840	*1, 020	
0.081.....	710	1, 180	1, 520	2, 340	-----	-----	-----	625	940	1, 110	
0.091.....	720	1, 190	1, 540	2, 410	-----	-----	-----	-----	1, 030	1, 200	
0.102.....	-----	-----	1, 560	2, 480	-----	-----	-----	-----	1, 100	1, 420	
0.125.....	-----	-----	1, 580	2, 590	-----	-----	-----	-----	1, 160	1, 470	
Rivet shear strength <sup>4</sup> .....	775	1, 190	1, 720	3, 110	775	1, 190	1, 720	-----	-----	-----	

YIELD STRENGTHS

0.008.....	150	180	220	-----	230	235	-----	-----	-----	-----
0.012.....	230	300	350	-----	320	362	320	-----	-----	-----
0.020.....	380	510	600	-----	400	620	650	-----	-----	-----
0.025.....	460	620	750	1, 090	450	705	808	-----	-----	-----
0.032.....	550	770	920	1, 380	510	810	980	80	-----	-----
0.040.....	620	850	1, 035	1, 660	570	900	1, 135	291	283	-----
0.051.....	660	930	1, 162	1, 938	-----	-----	-----	446	455	-----
0.064.....	680	1, 010	1, 282	2, 135	-----	-----	-----	541	610	412
0.072.....	700	1, 048	1, 334	2, 235	-----	-----	-----	572	690	604
0.081.....	710	1, 081	1, 391	2, 323	-----	-----	-----	593	776	811
0.091.....	720	1, 110	1, 450	2, 410	-----	-----	-----	608	869	991
0.102.....	-----	-----	1, 507	2, 480	-----	-----	-----	621	903	1, 150
0.125.....	-----	-----	1, 580	2, 590	-----	-----	-----	644	920	1, 334

<sup>1</sup> In dimpled installations allowables shall not be obtained by extrapolation for skin gages other than those shown.

<sup>2</sup> In the case of machine countersunk joints where the lower sheet is thinner than the upper, the bearing allowable for the lower sheet-rivet combination should be computed.

<sup>3</sup> Sheet gage is that of the thinnest sheet for protruding head and double-dimpled installations. For machine countersunk installations sheet gage is that of the upper sheet.

<sup>4</sup> Rivet shear strengths computed using nominal hole size and the following values for rivet and pin materials.

Rivet—R monel, annealed— $F_{su}$ =55,000 p. s. i.

Pin—R monel, cold worked— $F_{su}$ =65,000 p. s. i.

Yield values of the sheet-rivet combinations marked thus (\*) are less than  $\frac{3}{4}$  of the indicated ultimate values. Other sheet-rivet combinations may be used subject to specific approval of the procuring or certifying agency.

section shall be analyzed on the basis of its loading, allowables, dimensions, and geometry.

2.6122 *Effect on adjacent parent metal when fusion (arc or gas) processes are employed.* Joints—welded after heat treatment: The allowable stresses near the weld are given in tables 2.6122.

Materials heat treated after welding: The allowable stresses in the parent metal near a welded joint may equal the allowable stress for the material in the heat treated condition as given in tables 2.111.

Table 2.6122 (a). Allowable Ultimate Tensile Stresses Near Fusion Welds in 4130, 4140, 4340, or 8630 Steels

[Section thickness  $\frac{1}{4}$  inch or less]

Type of joint	Welded after heat treated or normalized after weld (p. s. i.)
Tapered joints of 30° or less <sup>1</sup> -----	90,000
All others-----	80,000

<sup>1</sup> Gussets or plate inserts considered 0° taper with center line.

Table 2.6122 (b). Allowable Bending Modulus of Rupture Near Fusion Welds in 4130, 4140, 4340, or 8630 Steels

Type of weld	Welded after heat treated or normalized after weld
Tapered welds of 30° or less. <sup>1</sup>	$F_b$ , fig. 2.321 for $F_{tu}=90,000$ p. s. i.
All others-----	$F_b$ , fig. 2.321 for $F_{tu}=80,000$ p. s. i.

<sup>1</sup> Gussets or plate inserts considered 0° taper with center line.

2.6123 *Allowable strength—weld metal.* Allowable weld metal joint strengths are given in table 2.6123.

When heat treatable welding rod or electrode MIL-E-6843 class C or D MIL-R-5632 grade 2G) is used and the structure is heat treated after welding, higher allowable stresses for the weld metal may be used when approved by the procuring or certifying agency. Representative tests shall be made and suitable reports submitted with the request for increase in stress value. Design allowable stresses for the weld metal shall be based on values not greater than 85 percent of the respective reliable minimum test values.

2.6124 *Welded cluster.* In welded structure where seven or more members converge, the allowable stress shall be determined by dividing the normal allowable stress by a materials factor of 1.5, unless the joint is reinforced in a manner for which specific authority has been obtained from the licensing or procuring agency. A tube that is continuous through a joint should be assumed as two members.

2.6125 *Flash welds.* The tension ultimate allowable stresses and bending allowable modulus of rupture for flash welds are given in tables 2.6125. A higher efficiency may be permitted in special cases by the applicable procuring or certifying agency upon approval of the manufacturers process specification.

2.6126 *Spot welding.* The permissibility of the use of spot welding on structural steel parts is governed by the requirements of the procuring or certifying agency. Maximum design shear strengths for spot welds in various steel alloys are given in table 2.6126 (a). Table 2.6126 (b) gives the minimum allowable edge distance for the spot welds in steel alloys; these values may be reduced for nonstructural applications, or for applications not depended upon to develop full tabulated weld strength. The thickness ratio of the thickest sheet to the thinnest outer sheet in the combination should not exceed 3.1.

Table 2.6123. Weld Metal Joint Strengths

Material	Parent metal thickness	Welding rod or electrode	$F_{tu}$	$F_{tu}$
Low carbon steels-----			32,000	51,000
Heat treatable alloy steels-----	$> \frac{1}{8}$ inch-----	Nonheat treatable (MIL-E-6843, class A or B, or MIL-R-5632, grade 1G).	32,000	51,000
Heat treatable alloy steels-----	$\frac{1}{8}$ inch or less-----		43,000	72,000
Heat treatable alloy steels-----	$> \frac{1}{8}$ inch $< \frac{1}{4}$ inch *-----	Heat treatable (MIL-E-6843, class C or D, or MIL-R-5632, grade 2G).	43,000	72,000

\*When the thickness  $t$ , exceeds  $\frac{1}{4}$  inch, suitable values shall be determined from representative tests, and data submitted for approval by the procuring or certifying agency.

Table 2.6125 (a). Allowable Ultimate Tensile Stresses for Flash Welds in Steel Tubing

Normalized tubing—not heat treated (including normalizing) after welding	Heat treated tubing welded after heat treatment	Tubing heat treated (including normalizing) after welding	
		$F_{tu}$ of unwelded material in heat treated condition	Allowable ultimate tensile stress of welds
$1.0 F_{tu}$ (based on $F_{tu}$ of normalized tubing).	$1.0 F_{tu}$ (based on $F_{tu}$ of normalized tubing).	< 100,000 100,000 to 150,000 > 150,000	$0.9 F_{tu}$ $0.6 F_{tu} + 30,000$ $0.8 F_{tu}$

Table 2.6125 (b) Allowable Bending Modulus of Rupture for Flash Welds in Steel Tubing


Normalized tubing—not heat treated (including normalizing) after welding	Heat-treated tubing welded after heat treatment	Tubing heat treated (including normalizing) after welding	
		$F_b$ from fig. 2.321 using values of $F_{tu}$ listed below	
$1.0 F_{tu}$ for normalized tubing-----	$1.0 F_{tu}$ for normalized tubing----	$F_{tu}$ of unwelded material in heat treated condition. < 100,000 100,000 to 150,000 > 150,000	Ultimate tensile stress for use in fig. 2.321 for $F_b$ of welded area. $0.9 F_{tu}$ $0.6 F_{tu} + 30,000$ $0.8 F_{tu}$

Table 2.6126 (a). Spotweld maximum design shear strength standards for uncoated steels<sup>1</sup> and nickel alloys

Nominal thickness of thinner sheet (inches)	Material ultimate tensile strength (150 ksi and above)	Material ultimate tensile strength (70 ksi to 150 ksi)	Material ultimate tensile strength (below 70 ksi)
	Pounds	Pounds	Pounds
0.006-----	70	57	-----
0.008-----	120	85	70
0.010-----	165	127	92
0.012-----	220	155	120
0.014-----	270	198	142
0.016-----	320	235	170
0.018-----	390	270	198
0.020-----	425	310	225
0.025-----	580	425	320
0.030-----	750	565	403
0.032-----	835	623	453
0.040-----	1, 168	850	650
0.042-----	1, 275	920	712
0.050-----	1, 700	1, 205	955
0.055-----	1, 982	1, 308	1, 130
0.060-----	2, 265	1, 558	1, 310
0.064-----	2, 550	1, 727	1, 437
0.070-----	2, 975	1, 982	1, 628
0.072-----	3, 048	2, 067	1, 685
0.080-----	3, 540	2, 405	1, 960
0.090-----	4, 100	2, 810	2, 290
0.094-----	4, 288	2, 975	2, 443
0.100-----	4, 575	3, 200	2, 645
0.109-----	4, 955	3, 540	2, 938
0.114-----	5, 177	3, 695	3, 084
0.125-----	5, 665	4, 052	3, 440

<sup>1</sup> Refers to plain carbon steels containing not more than 0.20 percent carbon and to austenitic steels.

Table 2.6126 (b). Minimum Edge Distances for Spot-welded Joints

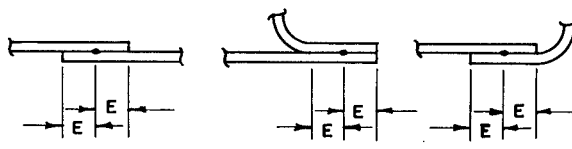

Thickness thinner sheet (inches)	Edge distance E	Thickness thinner sheet (inches)	Edge distance E
	Inches		Inches
0.016-----	$\frac{3}{16}$	0.060-----	$\frac{11}{32}$
0.020-----	$\frac{3}{16}$	0.070-----	$\frac{3}{8}$
0.025-----	$\frac{7}{32}$	0.080-----	$\frac{13}{32}$
0.030-----	$\frac{1}{4}$	0.090-----	$\frac{7}{16}$
0.035-----	$\frac{1}{4}$	0.100-----	$\frac{7}{16}$
0.040-----	$\frac{9}{32}$	0.120-----	$\frac{1}{2}$
0.045-----	$\frac{5}{16}$	0.125-----	$\frac{7}{16}$
0.050-----	$\frac{5}{16}$	0.157-----	$\frac{3}{4}$

## NOTES

Intermediate gages will conform to the requirement for the next thinner gage shown.

For edge distances less than those specified above, appropriate reductions in the spotweld allowable loads shall be made. These reductions shall be subjected to approval by the procuring or certifying agency.

2.61261 Reduction in tensile strength of parent metal due to spotwelding. In applications of spotwelding where ribs, intercostals, or doublers are attached to sheet splices or at other points on the sheet panels, the allowable ultimate tensile strengths of spotwelded sheet shall be determined by multiplying the ultimate tensile sheet strength.

obtained from tables 2.111 (c) by that appropriate efficiency factor shown on figures 2.6127 (a), 2.6127 (b) and 2.6127 (c).

Allowable ultimate tensile strengths for spot-welded sheet gages of less than 0.012 inch shall be established on the basis of tests acceptable to the procuring or certifying agency.

2.613 *Brazed joints of steel and high melting-point nonferrous alloys.* Brazing is defined as a weld wherein coalescence is produced by heating to suitable temperatures above 800° F. and by using a nonferrous filler metal having a melting point below that of the base metal. The filler metal is distributed through the joint by capillary attraction.

The effect of the brazing process upon the strength of the parent or base metal shall be considered in the structural design. Where copper furnace brazing or silver brazing is employed, the calculated allowable strength of the base metal which is subjected to the temperatures of the brazing process shall be in accordance with the following:

*Material*

Heat-treated material (including normalized) used in "as brazed" condition.

Heat-treated material (including normalized) reheat-treated during or after brazing.

*Allowable strength*

Mechanical properties of normalized material.

Mechanical properties corresponding to heat-treatment performed.

2.6131 *Copper brazing.* The allowable shear stress for design shall be 15,000 p. s. i., for all conditions of heat treatment. Higher values may be allowed upon approval by the procuring or certifying agency.

2.6132 *Silver brazing.* The allowable shear stress for design shall be 15,000 p. s. i., provided that clearances or gaps between parts to be brazed do not exceed 0.010 inch. Silver brazed areas should not be subjected to temperatures exceeding 900° F. Acceptable brazing alloys, with the exception of class 3, are listed in Federal Specification QQ-S-561d. Deviation from these

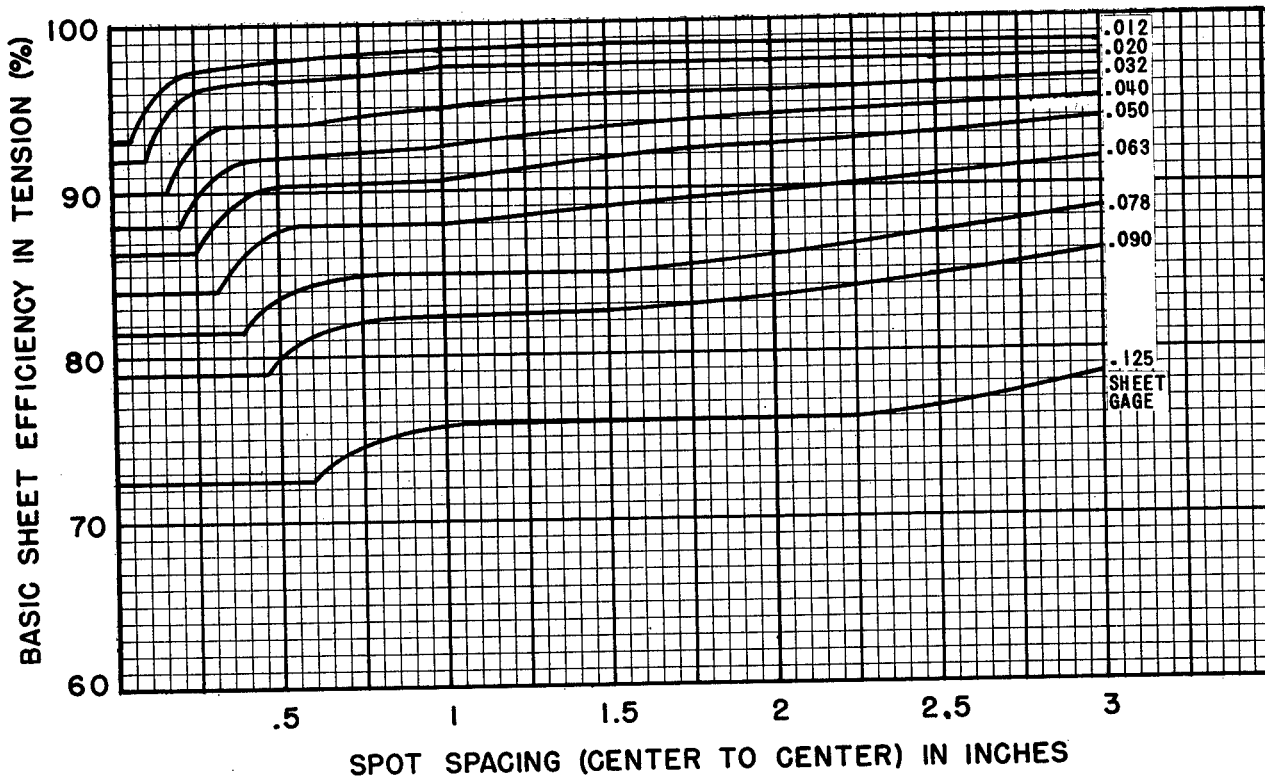


Figure 2.61261 (a). Efficiency of the parent metal in tension for spotwelded 302-1A, 347-A and 302-1/4H corrosion resisting steel.

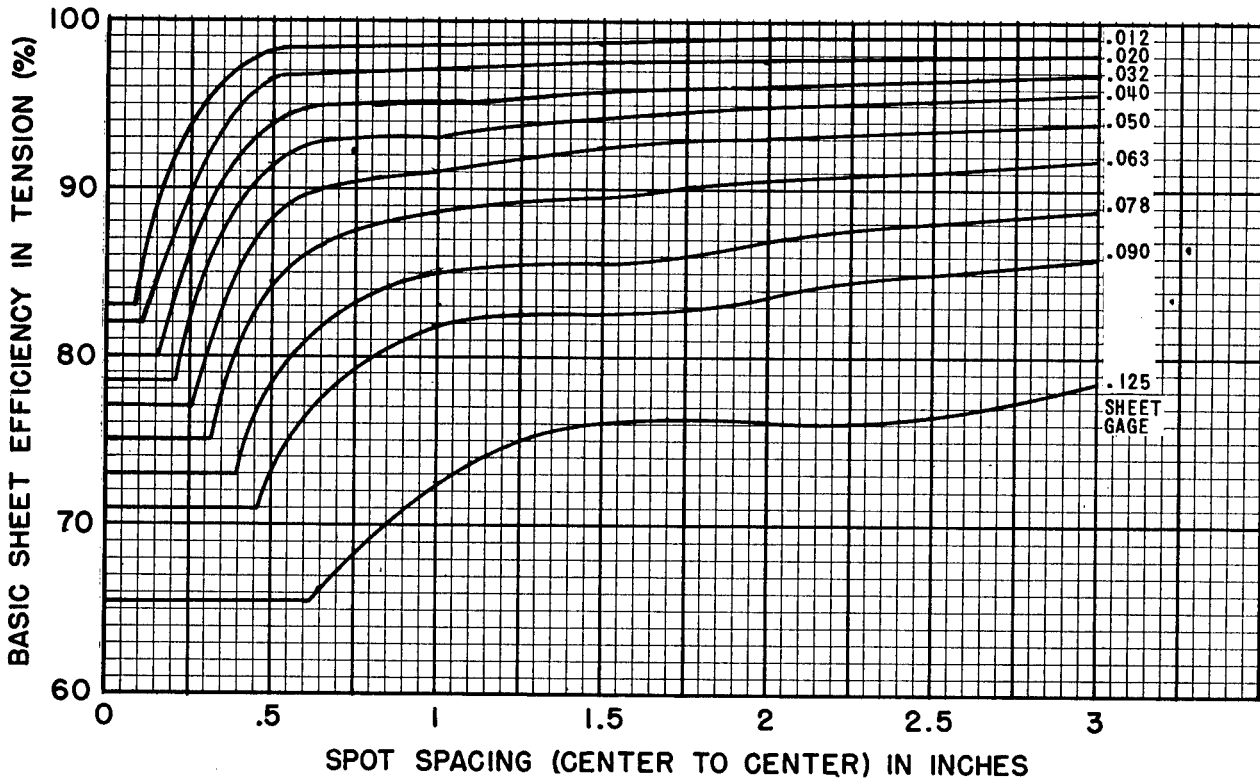


Figure 2.61261 (b). Efficiency of the parent metal in tension for spotwelded 302-1/2H corrosion resisting steel.

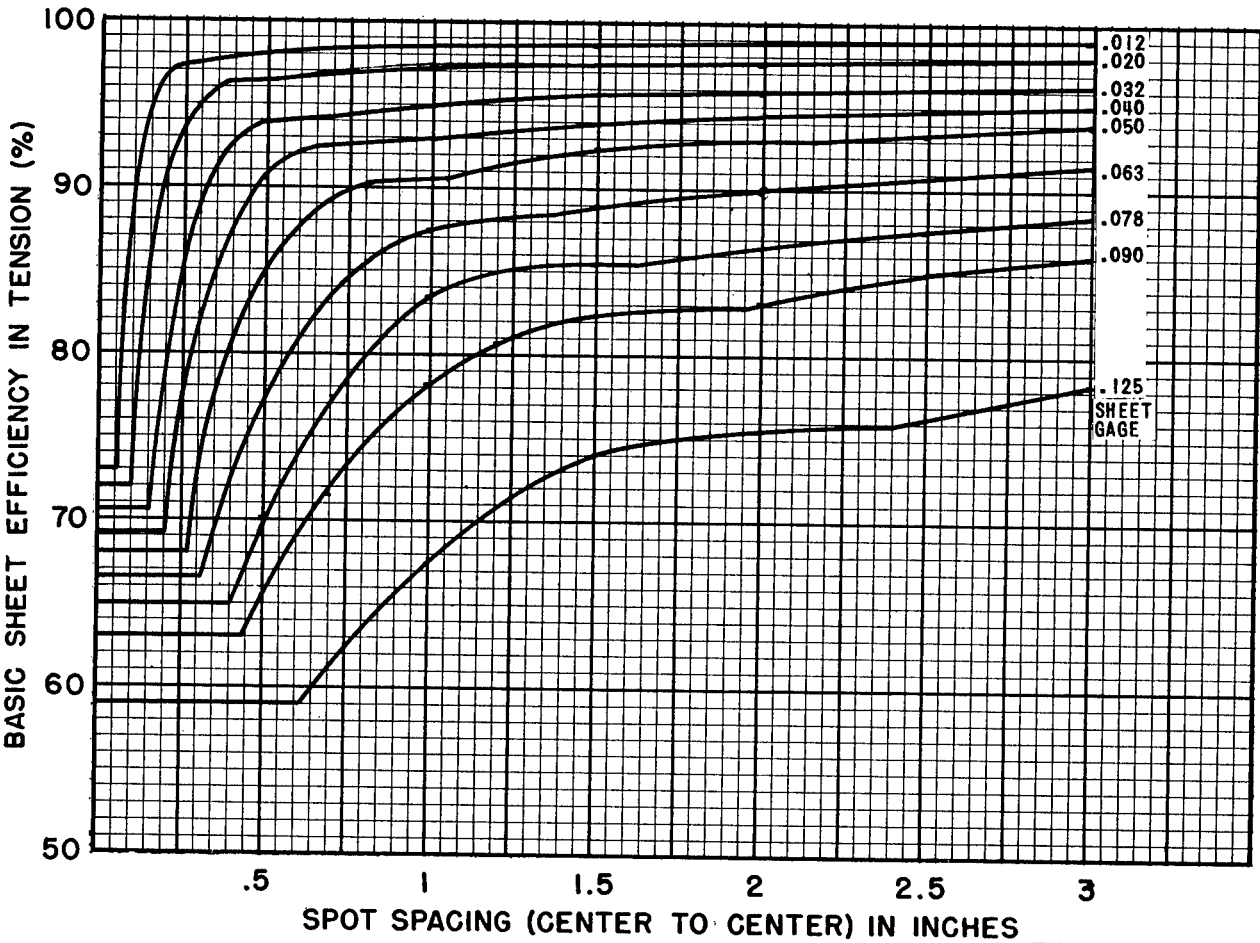


Figure 2.61261 (c). Efficiency of the parent metal in tension for spotwelded 302-H corrosion resisting steel.

specified allowable values or alloys may be allowed upon approval of the procuring or certifying agency.

2.614 *Adhesive bonded joints.* Joints may in some instances be made to advantage by the use of an adhesive suitable for the structural bonding of metals. This subject is discussed in reference 2.614.

## 2.62 PARTS

2.621 *Antifriction bearings.* For antifriction bearings the following load should not exceed the manufacturer's non-Brinell rating:

(a) For Air Forces and civil use—limit load.

(b) For Navy use—the design yield load.

Needle and tapered-roller antifriction bearings

may be used subject to the procuring or certifying agency's approval.

2.622 *Antifriction bearing control pulleys.* Information on the strengths of antifriction bearing control pulleys is given in table 2.622. Two requirements for pulley design must be met:

1. Pulley strength as limited by the resultant load on the pulley bearing.

2. Pulley strength as limited by the pressure on the pulley sheave produced by a cable under load.

For an ultimate factor of safety of 1.5 or less, the ultimate strength is not critical and the pulleys need be checked for the design yield strengths only.

Table 2.622. Static Yield Strengths for Control Pulleys

AN pulley	Resultant radial strength	Cable strengths for cable diameter indicated (see note 1)						Thrust on flange	
		$\frac{1}{16}$	$\frac{3}{32}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{7}{32}$		$\frac{1}{4}$
219-2	480	307	460						37
219-3	480	307	460						37
219-4	920	307	460						37
219-5	920	307	460						37
220-1	500			830	1,040	1,250			87
220-2	1,680			830	1,040	1,250			87
220-3	2,500			830	1,040	1,250			87
220-4	2,500			830	1,040	1,250			87
221-1	2,800					2,620	3,060	3,500	125
221-2	4,900					2,620	3,060	3,500	125
221-3	7,000					2,620	3,060	3,500	125

NOTE 1. The cable strengths are the limiting values for the pulley sheaves and not for the cables themselves. However, for a factor of safety of 1.5 or less, cable strength is not critical if MIL-C-1511 specification cable is used. Cable breaking strength may be found in table 2.6232.

NOTE 2. Limit endurance strengths: The endurance limit is 50,000 revolutions and approximately  $(7,850 \times \text{sheave diameter})$  reversals when using the largest cable size specified above, 90° angle of wrap, and a resultant radial strength equal to  $\frac{1}{4}$  the resultant radial strength given in the table above.

NOTE 3. For material, see Specification MIL-P-7034.

## 2.623 Cable and cable connections

2.6231 *Cable connections.* The following efficiencies shall be used in the design of cable connections.

(a)<sup>1</sup> For swaged connections manufactured in accordance with specifications approved by the applicable procuring or certifying agency, 100 percent.

(b)<sup>2</sup> Five tuck and Nicopress<sup>3</sup> type splice—flexible cable, 75 percent.

<sup>1</sup> Terminals used for swaged connections shall be designed to preclude failure at a load less than the minimum cable strength given in table 2.6232.

<sup>2</sup> Nicopress type splice may be used in place of the five-tuck splice in secondary applications in which the cable diameter is  $\frac{3}{8}$  inch or smaller.

<sup>3</sup> For civil aircraft Nicopress terminals may be used up to full rated load of the cable when the cable is looped around a thimble.

(c) Shackle and ferrule loop terminal—hard wire, 85 percent.

(d) Wrapped and soldered splice—19-strand wire, 90 percent.

2.6232 *Strength and load-deformation data for aircraft cable.* Information on strengths of steel cable is given in table 2.6232 and load-deformation data in figure 2.6232. The data in figure 2.6232 represent average curves obtained from a series of tensile tests on long lengths of pre-stretched 7 by 19 aircraft cable (pre-stretched 60 percent of rated strength), corrosion-resistant MIL-C-5424 and carbon steel MIL-C-1511. It will be noted that three stages or ranges are shown; (3) a slack range which is not eliminated

by the prestretching, (1) a short transitional elastic range and (2) an apparent true elastic range. For design purposes (1) and (2) are also shown as a combined elastic range. The data are mainly for the corrosion-resistant cable but can be converted to those for carbon steel by multiplying by the ratio of modulus of elasticity

for the corrosion-resistant to that of carbon steel. This relation is also shown by the comparative data on the chart for tests on both types of cables of  $\frac{3}{16}$  inch diameter. It is realized that the load-deformation characteristics of cable may be affected by several variables, yet it is believed that the data in figure 2.6232 are satisfactory.

Table 2.6232. Strength of Steel Cable

Diameter in inches	1 x 7 and 1 x 19		7 x 7, 7 x 19, and 6 x 19 (IWRC)				
	Nonflexible, carbon		Flexible, carbon		Flexible, corrosion resisting		
	MIL-C-6940		MIL-C-1511		MIL-C-5424		
	Weight in pounds per 100 feet	Breaking strength (pounds)	Weight in pounds per 100 feet	Breaking strength (pounds)	Weight in pounds per 100 feet	Breaking strength (pounds)	
0.031	$\frac{1}{32}$	0.30	185				
0.047	$\frac{3}{64}$	0.52	375				
0.062	$\frac{1}{16}$	0.78	500	0.75	480	0.75	480
0.078	$\frac{5}{64}$	1.21	800				
0.094	$\frac{3}{32}$	1.75	1,200	1.53	920	1.53	920
0.109	$\frac{7}{64}$	2.60	1,600				
0.125	$\frac{1}{8}$	3.50	2,100	2.90	2,000	2.90	1,900
0.156	$\frac{5}{32}$	5.50	3,300	4.50	2,800	4.44	2,600
0.187	$\frac{3}{16}$	7.70	4,700	6.50	4,200	6.47	3,900
0.218	$\frac{7}{32}$	10.00	6,300	8.60	5,600	9.50	5,200
0.250	$\frac{1}{4}$	13.50	8,200	11.00	7,000	12.00	6,600
0.281	$\frac{9}{32}$			13.90	8,000	14.56	8,000
0.312	$\frac{5}{16}$	20.65	12,500	17.30	9,800	17.71	9,600
0.344	$\frac{11}{32}$			20.70	12,500		
0.375	$\frac{3}{8}$			24.30	14,400	26.45	13,000
0.437	$\frac{7}{16}$			35.60	17,600	35.60	17,600
0.500	$\frac{1}{2}$			45.80	22,800	45.80	22,800
0.562	$\frac{9}{16}$			59.00	28,500	59.00	28,500
0.625	$\frac{5}{8}$			71.50	35,000	71.50	35,000
0.750	$\frac{3}{4}$			105.20	49,600	105.20	49,600
0.875	$\frac{7}{8}$			143.00	66,500	143.00	66,500
1.000	1			187.00	85,400	187.00	85,400
1.125	$1\frac{1}{8}$			240.00	106,400	240.00	106,400
1.250	$1\frac{1}{4}$			290.00	129,400	290.00	129,400
1.375	$1\frac{3}{8}$			330.00	153,600	330.00	153,600
1.500	$1\frac{1}{2}$			420.00	180,500	420.00	180,500



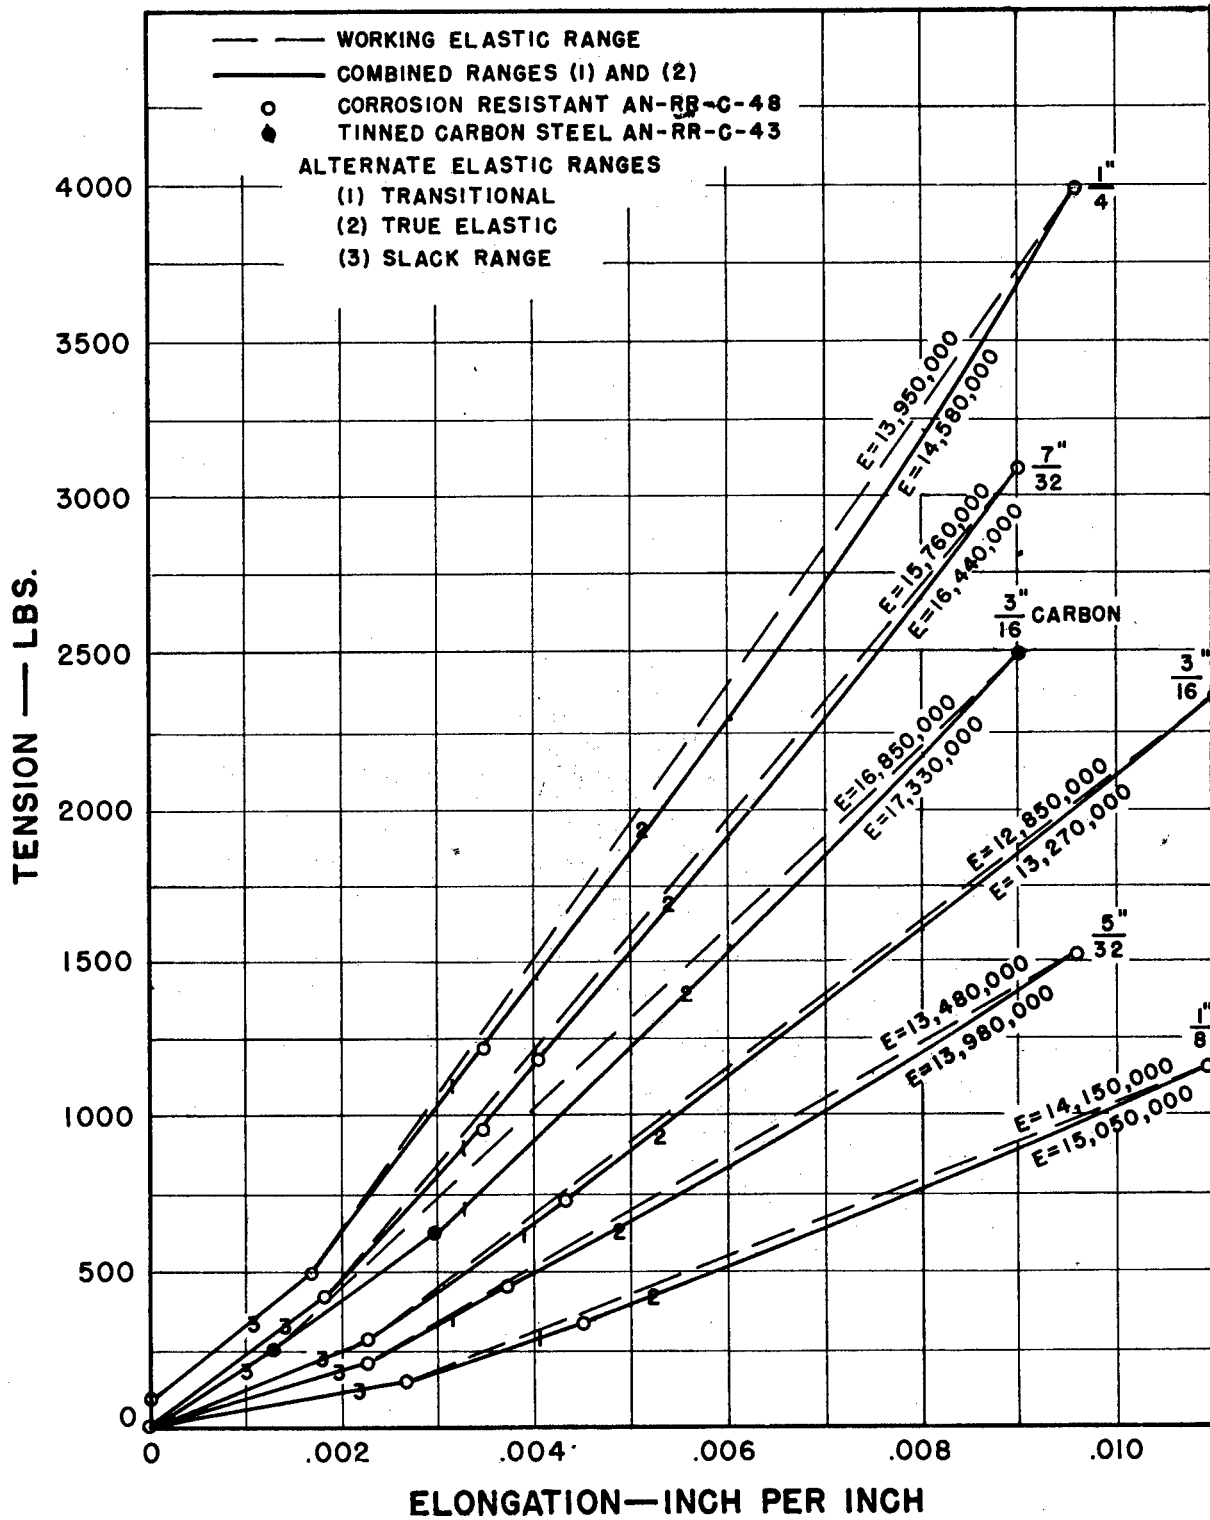


Figure 2.6232. Load—deformation data for steel cable.

## CHAPTER 3

### ALUMINUM ALLOYS

#### 3.1 General Properties

##### 3.11 NORMAL (ROOM) TEMPERATURE PROPERTIES

3.111 *Design mechanical properties.* The design mechanical properties at normal (room) temperature for various aluminum alloys are listed in tables 3.111. The values in the A column have been derived from test data and are the minimum values expected but are not necessarily covered by procurement specifications. All values in the B column have been derived from test data and are the lowest expected in 90 percent of the material. Use of the values in the B column is permitted in design by the Air Force, Navy and Civil Aeronautics Administration, subject to certain limitations as specified by each agency; reference should be made to the specific requirements of the applicable agency before using the B values in design. Tensile and compressive strengths have been given in both the longitudinal and transverse directions (parallel and perpendicular, respectively, to the direction of rolling, extruding, etc.) wherever data are available. Shear and bearing strengths have been given without reference to direction and may be assumed to be the same in all directions. In those instances where the direction in which the material will be used is not known, the lesser of the applicable longitudinal or transverse properties should be used.

In designing parts to be machined from large extrusions of 75S heat-treated and aged alloy, cognizance should be taken of the fact that, because of mass effect in quenching, the properties at the center of large sections of this alloy are generally lower than those midway between the center and the surface from which location the inspection samples are taken. The values given in table 3.111 (h) for longitudinal tensile and compressive properties and for shear and bearing strengths are based on the properties at the center for thicknesses less than 1.500 inches and on the properties midway between center and surface for

thicknesses 1.500 and over. These values are representative of the average property of the complete cross section. The values for transverse tensile and compressive properties are based on the properties at the center of the extrusion for all section thicknesses. Statistical studies have shown that the typical longitudinal properties at the center for 75S heat-treated and aged extrusions of section thickness 1.500–4.000 inches and up to 32 square inches area will be 94 and 91 percent, respectively, of the tensile ultimate and yield strength properties midway between the surface and center. It was further established that applying these ratios to the pertinent guaranteed minimums tabulated in table 3.111 (h) gave values most of which were equal or below the minimum center properties of all the large section extrusions tested. Based on the above therefore, footnotes (f) and (g) of table 3.111 (h) should be considered when designing a part machined from large extrusions of 75S heat-treated and aged alloy. When the part is heat-treated after rough machining, however, these footnotes may be disregarded.

The effects of notches, holes, and stress raisers on the static properties of aluminum alloys (see sec. 1.526) are given in references 3.111 (a), (b), (c), (d).

The transverse properties of aluminum alloy plate, bars, shapes, and hand forgings given in this document apply to the longer of the two transverse dimensions (width). There is some evidence that the transverse properties, measured at right angles to the above usual direction of testing transverse properties, are lower than the tabulated values. Sufficient data are not available, however, to permit the establishment of a quantitative relationship between the transverse properties in these two directions. Where sections are to be critically loaded in the transverse direction through the shorter dimension (thickness), this relationship should be established for the particular section and the need for correction of design allowables evaluated.

Table 3.111 (a). Design Mechanical Properties of Bare 24S Sheet and Plate (Kips Per Square Inch)

Type.....	Sheet and plate *												Coiled sheet						
	24S																		
	AN-A-12																		
Specification.....	Heat-treated																		
Condition.....	Heat-treated by user <sup>b</sup>				Heat-treated				Heat-treated and rolled				Heat-treated						
Thickness.....	0.250-0.500		1.001-2.000		2.001-3.000		<0.250		0.250-0.500		0.501-1.000		1.001-2.000		2.001-3.000		<0.250		
Basis <sup>c</sup> .....	A	A	A	A	A	A	A	A	B	A	B	A	B	A	B	A	B	A	B
$F_{tu}$ <sup>d</sup> .....	62	64	62	60	56	65	68	67	65	67	63	68	61	64	70	72	62	66	66
$T$ .....	62	64	62	60	56	64	67	66	64	66	62	67	60	63	59	71	62	66	66
$F_{ty}$ .....	40	38	38	38	38	48	51	46	48	49	44	48	42	46	60	62	40	41	41
$T$ .....	40	38	38	38	38	42	44	40	43	40	44	40	44	44	44	54	40	41	41
$F_{cy}$ .....	40	38	38	38	38	40	42	38	41	38	42	38	42	42	49	51	40	41	41
$T$ .....	40	38	38	38	38	45	47	43	46	43	47	42	46	46	56	58	40	41	41
$F_{su}$ .....	37	38	37	36	34	40	42	40	41	38	41	36	38	38	43	44	37	40	40
$F_{bru}$ ( $e/D=1.5$ ) <sup>f</sup> .....	93	96	93	90	84	98	102	98	101	95	102	92	96	96	105	108	93	99	99
$F_{brv}$ ( $e/D=2.0$ ).....	118	122	118	114	106	124	129	124	127	120	129	116	122	122	133	137	118	126	126
$F_{brv}$ ( $e/D=1.5$ ).....	56	53	53	53	53	69	71	64	69	62	67	60	66	66	84	88	56	57	57
$F_{brv}$ ( $e/D=2.0$ ).....	64	61	61	61	61	79	82	74	78	70	77	68	75	75	96	100	64	64	66
$E$ .....	10,500																		
$E_c$ .....	10,700																		
$G$ .....	4,000																		
W lbs./in. <sup>3</sup> .....	0.100																		
Commercial designations.....	24S-T4	24S-T42	24S-T3	24S-T4	24S-T3	24S-T4	24S-T4	24S-T4	24S-T4	24S-T4	24S-T4	24S-T4	24S-T4	24S-T4	24S-T36	24S-T4	24S-T4	24S-T4	24S-T4

<sup>a</sup> Plate is material which is greater than 0.249 inch thick.  
<sup>b</sup> Heat-treat by user refers to all material supplied in the annealed temper and heat-treated by the user, and to all material re-heat-treated by the user regardless of the temper in which the material was supplied.  
<sup>c</sup> A is the mechanical property column based upon minimum guaranteed tensile properties. (See par. 3.111.) B is the mechanical property column based upon probability data.  
<sup>d</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.  
<sup>e</sup> L=longitudinal (with grain); T=transverse (across grain). (See par. 3.111.)  
<sup>f</sup> D=hole diameter; e=edge distance measured from the hole center line in the direction of stressing; use value of e/D=2.0 for all larger values of edge distance; for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation; values for e/D less than 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

Table 3.111 (b). Design Mechanical Properties of Clad 24S Sheet and Plate (Kips per Square Inch)

Type.....	Sheet and plate *										Coiled sheet														
	Clad 24S																								
	AN-A-13																								
Condition.....	Heat-treated										Heat-treated and rolled	Heat-treated													
	Heat-treated by user <sup>b</sup>		0.010-0.063		0.064-0.249		0.250-0.499		0.500-1,000 <sup>c</sup>				1,001-2,000 <sup>c</sup>		2,001-3,000 <sup>c</sup>										
Thickness .....	<0.064	0.064-0.249	0.250-0.499	0.500-1,000 <sup>c</sup>	1,001-2,000 <sup>c</sup>	2,001-3,000 <sup>c</sup>	0.010-0.063		0.064-0.249		0.250-0.499		0.500-1,000 <sup>c</sup>		1,001-2,000 <sup>c</sup>		2,001-3,000 <sup>c</sup>								
	A	A	A	A	A	A	A	B	A	B	A	B	A	B	A	B	A	B							
$F_{tu}$ <sup>e</sup>	58	61	62	60	58	54	60	62	63	65	63	65	61	65	59	62	63	66	67	69	58	61	61	63	
$T_f$	58	61	62	60	58	54	59	61	62	64	62	64	60	64	58	61	54	62	65	66	68	58	61	61	63
$F_{ty}$	37	38	38	36	36	36	45	47	46	48	46	48	42	46	40	44	55	58	58	60	37	38	38	40	40
$F_{cy}$	37	38	38	36	36	36	37	39	38	40	38	40	36	42	38	42	48	50	50	52	37	38	38	40	40
$F_{su}$	37	38	38	36	36	36	42	44	43	45	41	45	40	44	44	51	54	54	54	56	37	38	38	40	40
$F_{brv}$ ( $e/D=1.5$ ) <sup>e</sup>	35	37	37	36	35	32	38	39	40	41	40	41	37	39	35	37	40	42	42	43	35	37	37	38	38
$F_{brv}$ ( $e/D=2.0$ )	87	92	93	90	87	81	90	93	95	98	95	98	92	98	89	93	95	99	101	104	87	92	92	95	95
$F_{brv}$ ( $e/D=1.5$ )	110	116	118	114	110	103	114	118	120	124	120	124	116	124	112	118	120	125	127	131	110	116	116	120	120
$F_{brv}$ ( $e/D=2.0$ )	52	53	53	50	50	50	64	67	64	69	64	69	59	64	56	62	77	81	81	84	52	53	53	56	56
$F_{brv}$ ( $e/D=2.0$ )	59	61	61	58	58	58	73	76	74	78	74	78	67	74	64	70	88	93	93	96	59	61	61	64	64
$E$	10,500	10,000	10,000	10,000	10,500	10,000	10,500	10,500	10,000	10,000	10,000	10,000	10,000	10,000	10,000	10,000	10,500	10,500	10,500	10,000	9,500	10,000	9,500	10,000	10,000
$E_c$	9,500	10,000	10,000	10,000	10,000	10,000	9,500	10,000	10,000	10,000	10,000	10,000	10,000	10,000	10,000	10,000	10,700	10,700	10,700	10,000	9,500	10,000	9,500	10,000	10,000
$G$	9,700	10,200	10,200	10,200	10,200	10,200	9,700	10,200	10,200	10,200	10,200	10,200	10,200	10,200	10,200	10,200	9,700	10,200	10,200	9,700	10,200	9,700	10,200	9,700	10,200
$W$ lbs./in. <sup>3</sup>	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100	0.100
Commercial designations.	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)	(Alclad 24S-T4)

<sup>a</sup> Plate is material which is greater than 0.249 inch thick.  
<sup>b</sup> Heat-treat by user refers to all material supplied in the annealed temper and heat-treated by the user, and to all material re-heat-treated by the user regardless of the temper in which the material was supplied.  
<sup>c</sup> Specification minimums for clad material 0.500 inch thick and heavier are for the core material inasmuch as a round test specimen is required for testing. The values given here for thickness 0.500 inch and greater have been adjusted to represent the average properties across the whole section including the cladding.  
<sup>d</sup> A is the mechanical property column based upon minimum guaranteed tensile properties; B is the mechanical property column based upon probability data. (See par. 3.111).  
<sup>e</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.  
<sup>f</sup> L=longitudinal (with grain); T=transverse (across grain). (See par. 3.111).  
<sup>g</sup> D=hole diameter; e=edge distance measured from the hole center line in the direction of stressing; use value of e/D=2.0 for all larger values of edge distance; for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation; values for e/D less than 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

Table 3.111 (c). Design Mechanical Properties of Clad 24S Sheet (Kips per Square Inch)

Type .....		Sheet							
		Clad 24S							
Alloy .....		AN-A-42							
		Heat-treated and aged		Heat-treated cold worked and aged					
Specification .....		<0.064	≥0.064	<0.064	≥0.064	<0.064	≥0.064	<0.064	≥0.064
		A		A		A		A	
Condition .....									
Thickness .....									
Basis <sup>a</sup> .....									
$F_{tu}^b$ .....	$L^c$ .....	60	62	64	67	67	70	70	72
	$T$ .....	60	62	62	65	65	66	66	70
$F_{ty}$ .....	$L$ .....	47	49	57	59	63	66	66	69
	$T$ .....	47	49	54	56	62	65	62	66
$F_{cy}$ .....	$L$ .....	47	49	55	57	62	65	63	66
	$T$ .....	47	49	55	57	63	65	63	66
$F_{su}$ .....		36	37	38	39	39	40	40	41
$F_{bru} (e/D=1.5)^d$ .....		90	93	96	100	100	105	105	106
$F_{bru} (e/D=2.0)$ .....		114	118	122	127	127	133	133	135
$F_{brv} (e/D=1.5)$ .....		66	69	78	83	88	92	91	95
$F_{brv} (e/D=2.0)$ .....		75	78	90	94	101	106	104	109
$E_t$ .....	PRI .....	10,500							
	SEC .....	9,500	10,000	9,500	10,000	9,500	10,000	9,500	10,000
$E_c$ .....	PRI .....	10,700							
	SEC .....	9,700	10,200	9,700	10,200	9,700	10,200	9,700	10,200
$G$ .....		0.100							
$W$ lb./in. <sup>3</sup> .....		0.100							
Commercial designations .....		Pureclad 24S-T6	Pureclad 24S-T81	Pureclad 24S-T84	Pureclad 24S-T86				
		Alclad 24S-T6	Alclad 24S-T81	Alclad 24S-T84	Alclad 24S-T86				

<sup>a</sup> A is the mechanical property column based upon the minimum guaranteed tensile properties.

<sup>b</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

<sup>c</sup> L=longitudinal (with grain) T=transverse (cross grain).

<sup>d</sup> D=hole diameter; e=edge distance measured from the hole center line in

the direction of stressing; use value of e/D=2.0 for all larger values of edge distance; for ratios between 1.5 and 2.0 the bearing stress value should be obtained by linear interpolation; values for e/D less than 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

Table 3.111 (d). Design Mechanical Properties of Clad 14S and R301 Sheet and Plate (Kips per Square Inch)

Type	Sheet (flat and coiled) and plate <sup>a</sup>				Flat sheet and plate <sup>a</sup>				Coiled sheet	Sheet (flat and coiled) and plate <sup>a</sup>			
Alloy	Clad 14S, R301								Clad 14S	Clad 14S, R301			
Specification	QQ-A-245												
Condition	Heat-treated by user				Heat-treated				Heat-treated and aged				
Thickness	≤0.039	0.040-0.249	0.250-0.499	0.500-1.000 <sup>b</sup>	≤0.039	0.040-0.249	0.250-0.499	0.500-1.000 <sup>b</sup>	≤0.039	0.040-0.128	≤0.039	0.040-0.499	0.500-1.000 <sup>b</sup>
Basis <sup>c</sup>	A	A	A	A	A	A	A	A	A	A	A	A	A
$F_{tu}$ <sup>d</sup>													
$L$ <sup>e</sup>	55	57	57	55	56	58	58	56	55	57	64	65	65
$T$	55	57	57	55	55	57	57	55	55	57	63	64	64
$T_{ty}$													
$L$	32	34	34	32	40	41	41	37	32	34	56	58	57
$T$	32	34	34	32	35	36	36	34	32	34	55	57	56
$F_{cy}$													
$L$	32	34	34	32	33	34	34	32	32	34	56	58	57
$T$	32	34	34	32	38	39	39	36	32	34	57	59	58
$F_{su}$	33	34	34	33	35	37	37	34	33	34	39	39	39
$F_{bru}(e/D=1.5)$ <sup>f</sup>	83	86	86	83	84	87	87	84	83	86	96	98	98
$F_{bru}(e/D=2.0)$	105	108	108	105	106	110	110	106	105	108	122	124	124
$F_{brv}(e/D=1.5)$	45	48	48	45	56	57	57	52	45	48	78	81	80
$F_{brv}(e/D=2.0)$	51	54	54	51	64	66	66	59	51	54	90	93	91
$E$	10,400												
$E_c$	10,600												
$G$	3,950												
$W$ lb./in. <sup>3</sup>	0.101												
Commercial designation	Hardclad R301-T4 Alclad 14S-T4	Hardclad R301-T42 Alclad 14S-T42	Hardclad R301-T3 Alclad 14S-T3	Hardclad R301-T4 Alclad 14S-T4	Hardclad R301-T4 Alclad 14S-T4	Hardclad R301-T6 Alclad 14S-T6							

<sup>a</sup> Plate is material which is greater than 0.249 inch thick.

<sup>b</sup> Specification minimums for clad material 0.500 inch thick and heavier are for the core material inasmuch as a round test specimen is required for testing. The values given here for thicknesses 0.500 inch and greater have been adjusted to represent the average properties across the whole section including the cladding.

<sup>c</sup> A is the mechanical property column based upon minimum guaranteed tensile properties.

<sup>d</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

<sup>e</sup>  $L$ =longitudinal (with grain);  $T$ =transverse (cross grain). (See par. 3.111.)

<sup>f</sup>  $D$ =hole diameter;  $e$ =edge distance measured from the hole center line in the direction of stressing; use value of  $e/D=2.0$  for all larger values of edge distance; for ratios between 1.5 and 2.0 the bearing stress value should be obtained by linear interpolation; values for  $e/D$  less than 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

Table 3.111 (e). Design Mechanical Properties of 75S Sheet and Plate (Kips per Square Inch)

Type.....		Sheet and plate <sup>a</sup>																	
		75S									Clad 75S								
Alloy.....		QQ-A-283									AN-A-10								
Specification.....		Heat-treated and aged																	
Condition.....																			
Thickness.....		0.016-0.039		0.040-0.249		0.250-0.500		0.501-1.000		1.001-2.000	0.016-0.039		0.040-0.249		0.250-0.499		0.500-1.000 <sup>b</sup>		1.001-2.000 <sup>b</sup>
Basis <sup>c</sup> .....		A	B	A	B	A	B	A	B	A	A	B	A	B	A	B	A	B	A
$F_{tu}$ <sup>d</sup> .....	L <sup>e</sup> .....	76	78	77	79	77	79	79	82	79	70	73	72	74	72	74	74	76	74
	T.....	76	78	77	79	77	79	77	80	77	70	73	72	74	72	74	72	74	72
$F_{ty}$ .....	L.....	66	69	67	70	67	69	69	72	69	61	64	63	65	63	65	64	67	64
	T.....	65	68	66	69	66	68	66	69	66	60	63	62	64	62	64	62	64	62
$F_{cy}$ .....	L.....	67	70	68	71	69	71	69	72	69	62	65	64	66	64	67	64	67	64
	T.....	70	73	71	74	69	71	69	72	69	64	67	66	68	64	67	64	67	64
$F_{su}$ .....		46	47	46	47	46	47	47	49	47	42	44	43	44	43	44	44	45	44
$F_{bru}(e/D=1.5)$ <sup>f</sup> .....		114	117	116	119	116	119	119	123	119	105	110	108	111	108	111	111	114	111
$F_{bru}(e/D=2.0)$ .....		144	148	146	150	146	150	150	156	150	133	139	137	141	137	141	141	144	141
$F_{brv}(e/D=1.5)$ .....		92	97	94	98	94	97	97	101	97	85	90	88	91	88	91	90	94	90
$F_{brv}(e/D=2.0)$ .....		106	110	107	112	107	110	110	115	110	98	102	101	104	101	104	102	107	102
$E$ .....	PRI.....	10, 300									10, 300								
	SEC.....										9, 500								
$E_c$ .....	PRI.....	10, 500									10, 500								
	SEC.....										9, 700								
$G$ .....		3, 900																	
$W$ lb./in. <sup>3</sup> .....		0. 101									0. 101								
Commercial designations.....		75S-T6									Alclad 75S-T6								

<sup>a</sup> Plate is material which is greater than 0.249 inch thick.

<sup>b</sup> Specification minimums for clad material 0.500 inch thick and heavier are for the core material inasmuch as a round test specimen is required for testing. The values given here for thickness 0.500 inch and greater have been adjusted to represent the average properties across the whole section including the cladding.

<sup>c</sup> A is the mechanical property column based upon minimum guaranteed tensile properties. (See par. 3.111.) B is the mechanical property column based upon probability data.

<sup>d</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

<sup>e</sup> L=longitudinal (with grain); T=transverse (cross grain). (See par. 3.111.)

<sup>f</sup> D=hole diameter; e=edge distance measured from the hole center line in the direction of stressing; use value of e/D=2.0 for all larger values of edge distance; for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation; values for e/D less than 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

Table 3.111 (f). Design Mechanical Properties of 52S and 61S Sheet (Kips per Square Inch)

Type.....		Sheet					
		52S				61S, R361	
Alloy.....		52S				61S, R361	
Specification.....		QQ-A-318 47A11				QQ-A-327	
Condition.....		¼ hard	½ hard	¾ hard	Full hard	Heat-treated	Heat-treated and aged
Thickness.....		0.016-0.249	0.013-0.249	0.013-0.162	0.013-0.128	<0.25	<0.25
Basis <sup>a</sup> .....		A	A	A	A	A	A
$F_{tu}$ <sup>b</sup> .....	$L^c$ .....	31	34	37	39	30	42
	$T$ .....	31	34	37	39	30	42
$F_{ty}$ .....	$L$ .....	21	24	29	33	16	36
	$T$ .....	20	23	29	33	16	35
$F_{cy}$ .....	$L$ .....	20	23				35
	$T$ .....	21	24				36
$F_{su}$ .....		19	20	22	23	20	27
$F_{brw}$ ( $e/D=1.5$ ) <sup>d</sup> .....		50	54	59	62	48	67
$F_{brw}$ ( $e/D=2.0$ ).....		65	71	78	82	63	88
$F_{brw}$ ( $e/D=1.5$ ).....		29	43	41	46	22	49
$F_{brw}$ ( $e/D=2.0$ ).....		34	38	46	53	26	56
$E$ .....			10, 100			9, 900	
$E_c$ .....			10, 200			10, 100	
$G$ .....			3, 850			3, 800	
$W$ lbs./in. <sup>3</sup> .....			0. 096			0. 098	
Commercial designations.....		52S-H32	52S-H34	52S-H36	52S-H38	{ 61S-T4 R361-T4	{ 61S-T6 R361-T6

<sup>a</sup> A is the mechanical property column based upon the minimum guaranteed tensile properties.

<sup>b</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

<sup>c</sup> L=longitudinal (with grain); T=transverse (cross grain). (See par. 3.111.)

<sup>d</sup> D=hole diameter; e=edge distance measured from the hole center line in

the direction of stressing; use value of  $e/D=2.0$  for larger values of edge distance; for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation; values for  $e/D$  less than the 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.



Table 3.111 (g). Design Mechanical Properties of Aluminum Alloy Rolled Bar and Rod, Tubing, and Shapes (Kips per Square Inch)

Type.....	Rolled bar, rod, and shapes						Tubing						
	14S	17S	24S		53S, R353	61S, R361	75S		24S		61S, R361		
Alloy.....	QQ-A-266	QQ-A-351	QQ-A-354	QQ-A-331	QQ-A-325			MIL-T-5063		WW-T-789 (MIL-T-7081)			
Specification.....	Heat-treated and aged	Heat-treated		Heat-treated and aged				Heat-treated	Heat-treated by user <sup>a</sup>		Heat-treated and aged		
Condition.....	$\geq \frac{3}{16}$ in., < 36 in. <sup>2</sup>	$\leq 3.000$	$\leq 3.000$	$\leq 3.000$	$\leq 3.000$	$\leq 3.000$	$\leq 3.000$	0.018 to 0.500	0.018 to 0.500	0.025 to 0.500			
Thickness and cross-section area.....	A	A	A	B	A	A	A	B	A	B	A	A	
Basis <sup>b</sup> .....													
$F_{tu}$ <sup>c</sup> .....	$L^d$ .....	65	55	62	64	32	42	77	80	64	70	62	42
	$T$ .....	62		50	52			70	73				
$F_{tv}$ .....	$L$ .....	55	32	40	43	25	35	66	70	42	46	40	35
	$T$ .....	53		37	40			60	63				
$F_{cv}$ .....	$L$ .....	55	32	40	43	25	35	66	70	42	46	40	35
	$T$ .....	53		37	40			60	63				
$F_{su}$ .....		38	33	37	38	19	25	46	48	39	42	39	27
$F_{bru}$ ( $e/D=1.5$ ) <sup>e</sup> .....		98	83	93	96	51		100	104	96	105	96	67
$F_{bru}$ ( $e/D=2.0$ ).....		124	105	118	122	67		123	128	122	133	122	88
$F_{brv}$ ( $e/D=1.5$ ).....		77	45	56	60	35		86	90	59	64	56	49
$F_{brv}$ ( $e/D=2.0$ ).....		88	51	64	69	40		92	98	67	74	64	56
$E$ .....		10,500	10,400	10,500		9,900	9,900	10,300		10,500		9,900	
$E_c$ .....		10,700	10,600	10,700		10,100	10,100	10,500		10,700		10,100	
$G$ .....		4,000	3,950	4,000		3,800	3,800	3,900		4,000		3,800	
$W$ lbs./in. <sup>3</sup> .....		0.101	0.101	0.100		0.097	0.098	0.101		0.100		0.098	
Commercial designations.....		14S-T6	17S-T4	24S-T4	{	53S-T6 R353-T6	{	61S-T6 R361-T6	75S-T6	24S-T3	24S-T4	{	61S-T6 R361-T6

<sup>a</sup> Heat-treat by user refers to all material supplied in the annealed temper and heat-treated by the user, and to all material re-heat-treated by the user regardless of the temper in which the material was supplied.

<sup>b</sup> A is the mechanical property column based upon the minimum guaranteed tensile properties; B is the mechanical property column based upon probability data. (See par. 3.111.)

<sup>c</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

<sup>d</sup>  $L$ =longitudinal (with grain);  $T$ =transverse (cross grain). (See par. 3.111.)

<sup>e</sup>  $D$ =hole diameter;  $e$ =edge distance measured from the hole center line in the direction of stressing; use value of  $e/D=2.0$  for larger values of edge distance; for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation; values  $e/D$  less than the 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

Table 3.111 (h). Design Mechanical Properties of 14S and 75S Extruded Bar, Rod, and Shapes (Kips Per Square Inch)

Type.....	Extruded bar, rod, and shapes																								
	14S						75S																		
	Q-Q-A-261 and Q-Q-A-266						AN-A-11																		
Alloy.....	Heat-treated and aged						Heat-treated and aged																		
	0.125-0.499		0.500-0.749		≥0.750, ≤25 square inch		≤0.750, >25 square inch and <32 square inch		Heat-treated and aged by user <sup>a</sup>		Up to 0.249 inch		0.250-2.999 inch		1.500-2.999 inch		3.000-4.499 inch <20 square inch		3.000-4.499 inch >20 square inch and <32 square inch		4.500-5.000 inch <32 square inch				
Condition.....	A		B		A		B		A		A		A		B		A		A		A				
	Thickness <sup>b</sup> and cross-section area.....																								
Basis <sup>c</sup> .....																									
$F_{tu}$ <sup>d</sup> .....	60	61	64	68	68	73	68	68	60	60	78	83	80	86	83	80	80	78	78	78	78	78			
$T$ .....	54	55	58	61	61	64	---	---	54	54	66	69	69	69	69	64	64	62	62	62	62	62	62		
$F_{ty}$ .....	53	57	58	62	60	65	58	58	53	53	70	76	72	78	75	70	70	70	70	70	70	70	70	70	
$T$ .....	48	51	52	56	54	58	---	---	48	48	58	61	58	61	61	56	56	56	56	56	56	56	56	56	
$F_{cy}$ .....	55	59	60	64	62	67	---	---	53	53	70	76	72	78	75	72	72	72	72	72	72	72	72	72	72
$T$ .....	53	56	62	62	57	61	---	---	48	48	70	76	65	70	68	65	65	65	65	65	65	65	65	65	65
$F_{su}$ .....	35	35	37	39	39	42	---	---	35	35	43	46	44	47	46	44	44	44	44	44	44	44	44	44	44
$F_{bru}$ ( $e/D=1.5$ ) <sup>b</sup> .....	90	92	96	102	90	95	---	---	101	101	101	108	96	103	100	103	103	103	103	103	103	103	103	103	103
$F_{bru}$ ( $e/D=2.0$ ).....	114	116	122	129	114	117	---	---	125	125	133	133	128	138	133	138	138	138	138	138	138	138	138	138	138
$F_{brv}$ ( $e/D=1.5$ ).....	74	80	81	87	78	85	---	---	91	91	99	99	79	86	83	86	86	86	86	86	86	86	86	86	86
$F_{brv}$ ( $e/D=2.0$ ).....	85	91	93	99	84	91	---	---	98	98	106	106	101	109	105	109	109	109	109	109	109	109	109	109	109
$E$ .....	10,500																								
$E_c$ .....	10,700																								
$G$ .....	4,000																								
$W$ lbs./in. <sup>3</sup> .....	0.101																								
Commercial designations.....	14S-T6												75S-T6												

<sup>a</sup> Heat-treat by user refers to all material supplied in the annealed temper and heat-treated by the user, and to all material re-heat-treated by the user regardless of the temper in which the material was supplied.

<sup>b</sup> For extrusions with outstanding legs, the load carrying ability of such legs shall be determined on the basis of the properties in the appropriate column corresponding to the leg thickness.

<sup>c</sup> A is the mechanical property column based upon minimum guaranteed tensile properties; B is the mechanical property column based upon probability data. (See par. 3.111.)

<sup>d</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

<sup>e</sup>  $L$ =longitudinal (with grain);  $T$ =transverse (cross grain). (See par. 3.111.)

<sup>f</sup> For parts machined from extrusions 1.500 inch and over in thickness so that the major load is carried by what was the center section of the extrusion, use 94 percent of this value for design. (See par. 3.111.)

<sup>g</sup> For parts machined from extrusions 1.500 inch and over in thickness so that the major load is carried by what was the center section of the extrusion, use 91 percent of this value for design. (See par. 3.111.)

<sup>h</sup>  $D$ =hole diameter;  $e$ =edge distance measured from the hole center line in the direction of stress; use value of  $e/D=2.0$  for all larger values of edge distance; for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation; values for  $e/D$  less than 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

Table 3.111 (i). Design Mechanical Properties of 24S and 61S Extruded Shapes (Kips Per Square Inch)

Type.....		Extruded shapes										
		24S										
Alloy.....		61S, R361										
Specification.....		QQ-A-325										
Condition.....		Heat-treated								Heat-treated by user <sup>a</sup>	Heat-treated and aged	
		<0.250		0.250 to 0.749		0.750 to 1.499		$\geq 1.500$ inches $\leq 25$ square inches				
Thickness <sup>b</sup> and cross-section area.....								0.250 and up $\leq 32$ square inches		Up to 3.000		
Basis <sup>c</sup> .....		A	B	A	B	A	B	A	B	A	A	
$F_{tu}$ <sup>d</sup> .....	$L$ <sup>e</sup> .....	57	61	60	60	65	70	70	74	57	38	
	$T$ .....	51	53	51	53	51	54	51	54	51	36	
$F_{ty}$ .....	$L$ .....	42	47	44	47	46	54	52	54	38	35	
	$T$ .....	36	39	36	39	37	42	39	41	36	33	
$F_{cy}$ .....	$L$ .....	38	41	39	42	44	52	50	52	38	35	
	$T$ .....	38	41	39	42	42	48	42	44	38	35	
$F_{su}$ .....		30	32	32	32	34	38	37	40	30	24	
$F_{bru}(e/D=1.5)$ <sup>f</sup> .....		85	91	85	91	85	91	85	91	85	61	
$F_{bru}(e/D=2.0)$ .....		108	114	108	114	108	114	108	114	108	80	
$F_{brv}(e/D=1.5)$ .....		59	66	60	66	61	66	62	66	53	49	
$F_{brv}(e/D=2.0)$ .....		67	75	69	75	71	75	73	75	61	56	
$E$ .....											9,900	
$E_c$ .....											10,100	
$G$ .....											3,800	
$W$ lbs./in. <sup>3</sup> .....											0.098	
Commercial designations.....										24S-T42	{	61S-T6 R361-T6

<sup>a</sup> Heat-treat by user refers to all material supplied in the annealed temper and heat-treated by the user, and to all material re-heat-treated by the user regardless of the temper in which the material was supplied.

<sup>b</sup> For extrusions with outstanding legs the load carrying ability of such legs shall be determined on the basis of the properties in the appropriate column corresponding to the leg thickness.

<sup>c</sup> A is the mechanical property column based upon the minimum guaranteed tensile properties; B is the mechanical property column based upon probability data. (See par. 3.111.)

<sup>d</sup> Standard structural symbols are explained in sec. 1.2 of ch. 1.

<sup>e</sup>  $L$ =longitudinal (with grain);  $T$ =transverse (cross grain). (See par. 3.111.)

<sup>f</sup>  $D$ =hole diameter;  $e$ =edge distance measured from the hole centerline in the direction of stressing; use value of  $e/D=2.0$  for all larger values of edge distance; for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation; values for  $e/D$  of less than 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

Table 3.111 (j). Design Mechanical Properties of 14S and 75S Hand Forged Stock (Kips per Square Inch)

Type	Hand-forged stock Length $\leq 3$ times width		Hand-forged stock Length $> 3$ times width		Parts from hand-forged stock Length $\leq 3$ times width		Parts from hand-forged stock Length $> 3$ times width	
	14S	AMS4135F	14S	AMS4139D	75S	AMS4139D	75S	AMS4139D
Alloy	AMS4135F							
Specification	AMS4139D							
Condition	Heat-treated and aged							
Cross section Area (in. <sup>2</sup> )	$\leq 16$	$\leq 16$	$\leq 16$	$\leq 16$	$\leq 16$	$\leq 16$	$\leq 16$	$\leq 16$
	$> 16$	$\leq 36$	$\leq 144$	$\leq 256$	$\leq 16$	$\leq 36$	$\leq 144$	$\leq 256$
Basis <sup>a</sup>	A	A	A	A	A	A	A	A
	A	A	A	A	A	A	A	A
$F_{tu}^b$	65	65	60	65	65	60	75	71
$T$	<sup>d</sup> 62	<sup>d</sup> 59	<sup>d</sup> 57	62	62	62	75	69
$F_{ty}$	55	53	48	55	53	48	64	62
$T$	<sup>e</sup> 55	<sup>e</sup> 50	<sup>e</sup> 48	53	51	48	63	61
$F_{cy}$	55	53	48	55	53	48	64	62
$T$	<sup>e</sup> 55	<sup>e</sup> 50	<sup>e</sup> 48	53	51	48	63	61
$F_{tu}$	40	40	37	40	40	37	63	61
$F_{bru}$ ( $e/D=1.5$ ) <sup>f</sup>	98	93	90	98	98	90		
$F_{bru}$ ( $e/D=2.0$ )	124	118	114	124	118	114		
$F_{brv}$ ( $e/D=1.5$ ) <sup>f</sup>	77	74	67	77	74	67		
$F_{brv}$ ( $e/D=2.0$ )	88	80	77	88	85	77		
$E_t$	10,500							
$E_c$	10,700							
$G$	4,000							
W lbs./in. <sup>3</sup>	0.101							
Commercial designations	14S-T6							

<sup>a</sup> A is the mechanical property column based upon minimum guaranteed tensile properties.  
<sup>b</sup> Standard structural symbols are explained in sec. 1.2 of ch. 1.  
<sup>c</sup> L—Longitudinal (with grain); T—Transverse (across grain in the longer of 2 transverse directions, width).  
<sup>d</sup> Short transverse dimension (thickness) is 3,000 pounds lower.  
<sup>e</sup> Short transverse dimension (thickness) is the same as long transverse.  
<sup>f</sup> Same as note f on table 3.111 (i).

Table 3.111 (k). Design Mechanical Properties of Aluminum Alloy Die Forgings (Kips per Square Inch)

Type.....		Die forgings					
		14S		25S	A51S	53S, R353	75S
Alloy.....		QQ-A-367					
Specification.....		Heat-treated and aged					
Condition.....		Heat-treated	Heat-treated and aged				
Thickness.....		≥4 inches					≤3 inches
Basis <sup>a</sup> .....		A	A	A	A	A	A
$F_{tu}$ <sup>b</sup> .....	$L$ <sup>c</sup> .....	55	65	55	44	36	75
	$T$ .....	52	62	52	42	34	71
$F_{tu}$ .....	$L$ .....	30	55	33	37	30	65
	$T$ .....	28	52	31	35	28	62
$F_{cu}$ .....	$L$ .....	30	55	33	37	30	65
	$T$ .....	28	52	31	35	28	58
$F_{su}$ .....		34	39	34	28	22	45
$F_{bru}$ ( $e/D=1.5$ ) <sup>d</sup> .....		83	98	83	70	58	-----
$F_{bru}$ ( $e/D=2.0$ ).....		105	124	105	92	76	-----
$F_{brv}$ ( $e/D=1.5$ ).....		42	77	46	52	42	-----
$F_{brv}$ ( $e/D=2.0$ ).....		48	88	53	59	48	-----
$E$ .....		10,500	10,500	10,300	10,100	9,900	10,300
$E_c$ .....		10,700	10,700	10,500	10,300	10,100	10,500
$G$ .....		4,000	4,000	3,900	3,850	3,800	3,900
$W$ lbs./in. <sup>3</sup> .....		0.101	0.101	0.101	0.097	0.097	0.101
Commercial designations.....		14S-T4	14S-T6	25S-T6	A51S-T6	R353-T6, 53S-T6	75S-T6

<sup>a</sup> A is the mechanical property column based upon minimum guaranteed tensile properties.

<sup>b</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

<sup>c</sup> L=longitudinal (with grain); T= transverse (cross grain).

<sup>d</sup> D=hole diameter; e=edge distance measured from the hole center line in

the direction of stressing; use value of  $e/D=2.0$  for all larger values of edge distance; for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation; values for  $e/D$  less than 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

Table 3.111 (l). Design Mechanical Properties of Aluminum Alloy Castings (Kips per Square Inch)

Type.....	Sand castings <sup>a</sup>					Permanent mold castings <sup>a</sup>			
	40-E	195-T4	195-T6	220-T4	356-T6	B195-T4	B195-T6	355-T6	356-T6
Alloy.....									
Specification.....	QQ-A-601	QQ-A-601		QQ-A-601	QQ-A-601	QQ-A-596		QQ-A-596	QQ-A-596
Condition.....	Aged	Heat-treated, class I	Heat-treated and aged, class II	Heat-treated	Heat-treated, and aged	Heat-treated class I	Heat-treated and aged, class II	Heat-treated and aged	
Basis <sup>b</sup> .....	A	A	A	A	A	A	A	A	A
$F_{tu}$ <sup>c</sup> .....	32	29	32	42	30	33	35	37	33
$F_{ty}$ .....	20	13	20	22	20	20	22	23	22
$F_{cy}$ .....		14	21	23	20	20	22	23	22
$F_{su}$ .....	27	22	24	30	25	25	26	26	25
$F_{bru}$ ( $e/D=1.5$ ) <sup>d</sup> .....		46	51	67	48				
$F_{bru}$ ( $e/D=2.0$ ).....		61	67	88	63				
$F_{brv}$ ( $e/D=1.5$ ).....		22	34	37	34				
$F_{brv}$ ( $e/D=2.0$ ).....		26	40	44	40				
$E$ .....						10,300			
$E_c$ .....						10,300			
$G$ .....						3,850			
$W$ lbs./in. <sup>3</sup> .....	0.100	0.101	0.101	0.093	0.097	0.101	0.101	0.098	0.097
Commercial designation.....	40-E	195-T4	195-T6	220-T4	356-T6	B195-T4	B195-T6	355-T6	356-T6

<sup>a</sup> Reference should be made to the specific requirements of the procuring or certifying agency in regard to the use of the above values in the design of castings.

<sup>b</sup>A is the mechanical property column based upon the minimum guaranteed tensile properties from separately cast test bars.

<sup>c</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

<sup>d</sup>  $D$ =hole diameter;  $e$ =edge distance measured from the hole center line in the direction of stressing; use value of  $e/D=2.0$  for all large values of edge distance; for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation; values for  $e/D$  of less than 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.

3.112 *Fatigue properties.* Rotating-beam, repeated-flexure, and direct-stress tension-compression fatigue strength data at normal (room) temperature, for several aluminum alloy materials are given in tables 3.112 (a) through (d). These data are average values. Even under carefully controlled conditions, there is considerable scatter in fatigue test results. The tabulated test results, therefore, must be considered as values lying at about the center of a scatter band which may in some cases be broad enough to include values 20 percent above and below the average curves. (See reference 3.112 (a) for effect of grain direction on fatigue properties of aluminum alloys.)

The values given in most of the tables are determined on smooth specimens, that is, on specimens in which stress concentrations are purposely minimized. They do not apply directly to the design of structures because they do not take account of the effect of stress raisers such as reentrant corners, notches, holes, joints, rough surfaces, and other similar conditions which are present in fabricated parts. The localized high stresses induced in fabricated parts by such stress raisers are of much greater importance for repeated loading

than they are for static loading. They reduce the fatigue life of fabricated parts far below that which would be predicted by comparing the smooth-specimen fatigue strengths directly with the nominal calculated stresses for the parts in question. Fabricated parts in test have been found to fail at less than 50,000 repetitions of load when the nominal stress was far below that which could be repeated many millions of times on a smooth machined specimen. (See reference 3.112 (b) for information on how to use high-strength aluminum-alloy and reference 3.112 (c) for further details on the static and fatigue strengths of high-strength aluminum-alloy bolted joints.) Reference 3.112 (d) presents single rivet fatigue test data.

One of the accompanying tables, table 3.112 (b), shows notch-fatigue data. The data in this table were obtained in the same kind of a test as that used to obtain the data in table 3.112 (a), except that the specimens were not smooth but contained a circumferential 60° very sharp V notch. By comparing table 3.112 (b) with table 3.112 (a), one can immediately see the serious effect that such a sharp notch has on fatigue strength. It is evi-

Table 3.111 (m). Design Mechanical Properties of Heat Treated, Cold Worked and Aged 24S Alloy Extrusions and Tubing (Kips per Square Inch)

Type.....	Extruded shapes	Tubing
	24S	24S
Alloy.....		
Specification.....		
Condition.....	Heat-treated, cold worked and aged	Heat-treated, cold worked and aged
Cross Section Area (in <sup>2</sup> ).....	≥0.250	
Basis <sup>a</sup> .....	A	A
$F_{tu}$ <sup>b</sup> .....	64	68
$F_{ty}$ .....	56	60
$F_{ey}$ .....		
$F_{su}$ .....		
$F_{bru}(e/D=1.5)$ .....		
$F_{bru}(e/D=2.0)$ .....		
$F_{brv}(e/D=1.5)$ .....		
$F_{brv}(e/D=2.0)$ .....		
$E$ .....	10, 500	10, 500
$E_c$ .....	10, 700	10, 700
$G$ .....	4, 000	4, 000
$W$ lbs./in. <sup>3</sup> .....	0. 100	0. 100
Commercial designations.....	24S-T81	24S-T81

<sup>a</sup> A is the mechanical property column based upon minimum guaranteed tensile properties.

<sup>b</sup> Standard structural symbols are explained in sec. 1.2 of ch. 1.

<sup>c</sup> L=longitudinal (with grain); T=transverse (across grain in the longer of 2 transverse directions; width).

Table 3.112 (a). Average Fatigue Strengths of Smooth Machined Round Specimens Under Completely Reversed Flexure

[Values given are from tests of 0.3-inch diameter machined specimens in R. R. Moore rotating-beam fatigue machines at Aluminum Research Laboratories. Tests of specimens up to 2-inch diameter show no appreciable size effect]

Alloy and temper	Fatigue strength (reversed stress) ksi at indicated number of cycles					
	10,000 cycles	100,000 cycles	1,000,000 cycles	10,000,000 cycles	100,000,000 cycles	500,000,000 cycles
14S-T6.....	53	40	31	25	20	18
24S-T4.....	53	40	31	25	20	18
A51S-T6.....	41	29	21	16	12	11
61S-T6.....	43	31	22	17	14	13
75S-T6.....	56	42	31	25	22	21

Table 3.112 (b). Average Fatigue Strengths of Sharply Notched Round Specimens Under Completely Reversed Flexure.

[Values given are from tests of sharply notched specimens in R. R. Moore rotating-beam fatigue machines at Aluminum Research Laboratories. Each specimen was 0.480 inch in diameter and contained a circumferential 60° V notch, 0.075 inch deep with a radius at the base of the notch of about 0.0002 inch. The values given in the table are nominal calculated stresses obtained by applying the simple flexure formula to the 0.330-inch diameter cross section at the root of the notch with no correction for stress concentration]

Alloy and temper	Fatigue strength (reversed stress) ksi at indicated number of cycles					
	10,000 cycles	100,000 cycles	1,000,000 cycles	10,000,000 cycles	100,000,000 cycles	500,000,000 cycles
14S-T6.....	31	20	14	10	8	8
24S-T4.....	33	24	17	13	11	11
A51S-T6.....	28	16	9	7	6	6
61S-T6.....	29	18	11	8	7	7
75S-T6.....	31	20	14	10	8	8

Table 3.112 (c). Average Fatigue Strengths of Flat Sheet Specimens Under Completely Reversed Flexure

[Values given are from tests of 0.064-inch thick sheet specimens with as-rolled surfaces in Aluminum Research Laboratories repeated flexure fatigue machines]

Alloy and temper	Fatigue strength (reversed stress) ksi at indicated number of cycles				
	100,000 cycles	1,000,000 cycles	10,000,000 cycles	100,000,000 cycles	500,000,000 cycles
24S-T3.....	34	26	21	18	18
24S-T36.....	37	29	22	19	19
61S-T6.....	30	22	16	13	12
75S-T6.....	37	26	21	20	20
Alclad 14S-T3.....	31	20	17	15	15
Alclad 14S-T6.....	31	20	17	15	15
Alclad 24S-T3.....	31	19	15	13	13
Alclad 24S-T36.....	31	19	15	13	13
Alclad 24S-T81.....	31	19	15	13	13
Alclad 24S-T86.....	31	19	15	13	13
Alclad 75S-T6.....	31	19	15	13	13

Table 3.112 (d). Average Fatigue Strengths of Smooth Machined Round Specimens Under Repeated Axial Load

[Values given are from tests of 0.2-inch diameter specimens in Aluminum Research Laboratories direct-stress fatigue machines. Stresses considered algebraically: plus (+) means tension, minus (-) means compression]

Alloy and temper	Mean (steady) stress, ksi	Reversed (alternating) stress, ksi, at indicated number of cycles				
		100,000 cycles	1,000,000 cycles	10,000,000 cycles	100,000,000 cycles	500,000,000 cycles
14S-T6 and 24S-T4	-10	± 33	± 26	± 21	± 18	± 17
	- 5	± 33	± 26	± 21	± 17	± 16
	0	± 32	± 25	± 20	± 17	± 16
	+ 5	± 32	± 25	± 20	± 16	± 15
	+10	± 30	± 24	± 19	± 16	± 14
	+15	± 29	± 23	± 18	± 15	± 13
	+20	± 27	± 22	± 17	± 14	± 13
	+25	± 25	± 21	± 16	± 13	± 12
61S-T6	-10	± 28	± 22	± 17	± 13	± 11
	- 5	± 27	± 21	± 16	± 12	± 11
	0	± 26	± 20	± 16	± 12	± 11
	+ 5	± 25	± 19	± 15	± 12	± 11
	+10	± 23	± 18	± 14	± 12	± 11
	+15	± 21	± 17	± 14	± 12	± 11
	+20	± 19	± 15	± 13	± 11	± 11
75S-T6	-10	± 38	± 31	± 25	± 21	± 20
	- 5	± 37	± 30	± 23	± 20	± 19
	0	± 36	± 29	± 22	± 19	± 18
	+ 5	± 34	± 27	± 21	± 17	± 16
	+10	± 33	± 26	± 19	± 16	± 15
	+15	± 31	± 24	± 17	± 14	± 13
	+20	± 29	± 22	± 16	± 13	± 12

dent that all of the materials do not suffer to the same extent from the presence of a sharp notch. The notch fatigue strengths, like the smooth-specimen fatigue strengths, are not to be used as allowable stress values for design but are included for general information only.

3.113 *Typical stress-strain and tangent modulus data.* Typical stress-strain diagrams and tangent modulus values at various stresses are given in figures 3.113 for certain 24S and 14S aluminum alloy products.

The typical stress-strain curves may be converted to other values of  $F_{ty}$  and  $F_{cy}$  by the Ramberg-Osgood method or any other analytical or graphical method which maintains the original slope and results in a curve affine with the typical curve.

### 3.12 TEMPERATURE EFFECTS

#### 3.121 *Low temperature*

3.1211 *Static properties.* The approximate effect of low temperatures on the tensile properties of materials given in table 3.111 (a) through 3.111 (m) are shown in table 3.1211 (a). These static properties must be used with the same caution as applied to room temperature static properties relative to stress raisers. The effect of low temperature on the modulus of elasticity of aluminum alloys is given in table 3.1211 (b).

3.1212 *Fatigue properties.* The effect of low temperatures on unnotched reciprocating non-rotating round cantilever fatigue specimens is shown in table 3.1212. The combined effect of notches, holes, joints, etc., and low temperatures on fatigue strength is not well known, and such factors should be considered.



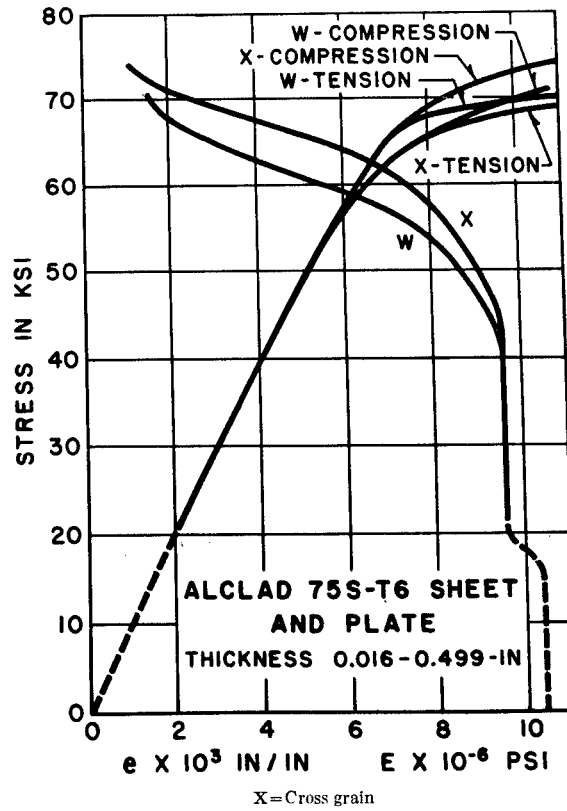
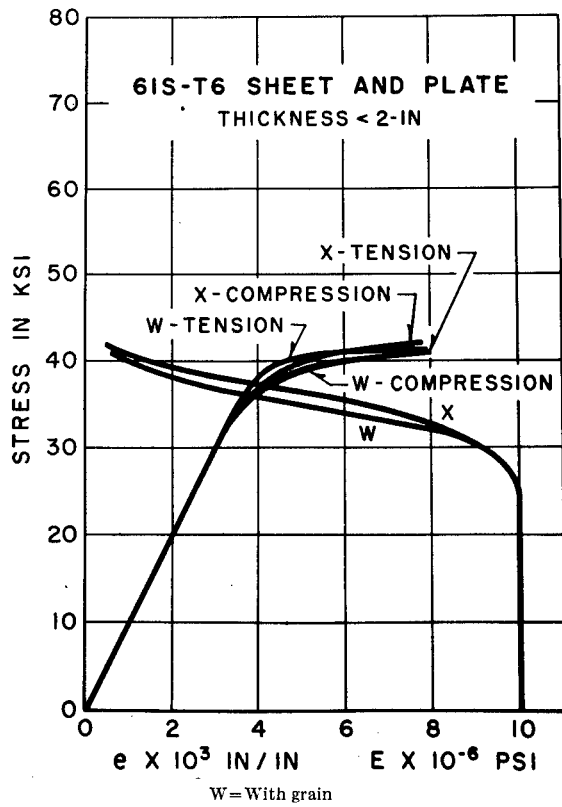
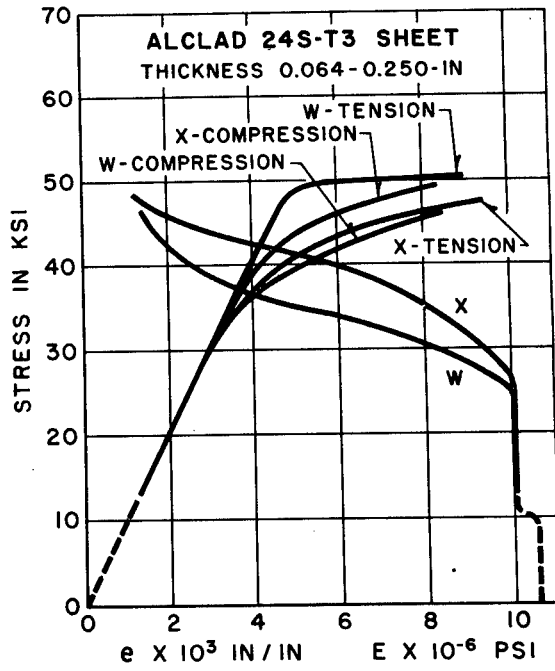
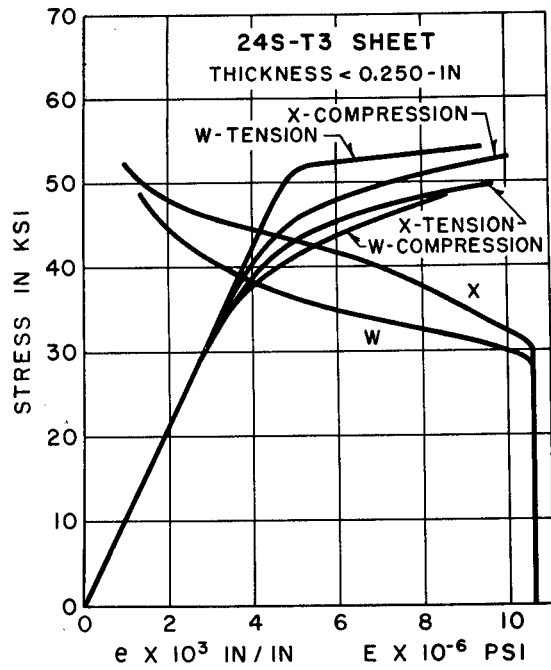


Figure 3.113 (a). Typical stress-strain and tangent modulus curves for various aluminum alloy sheet materials.

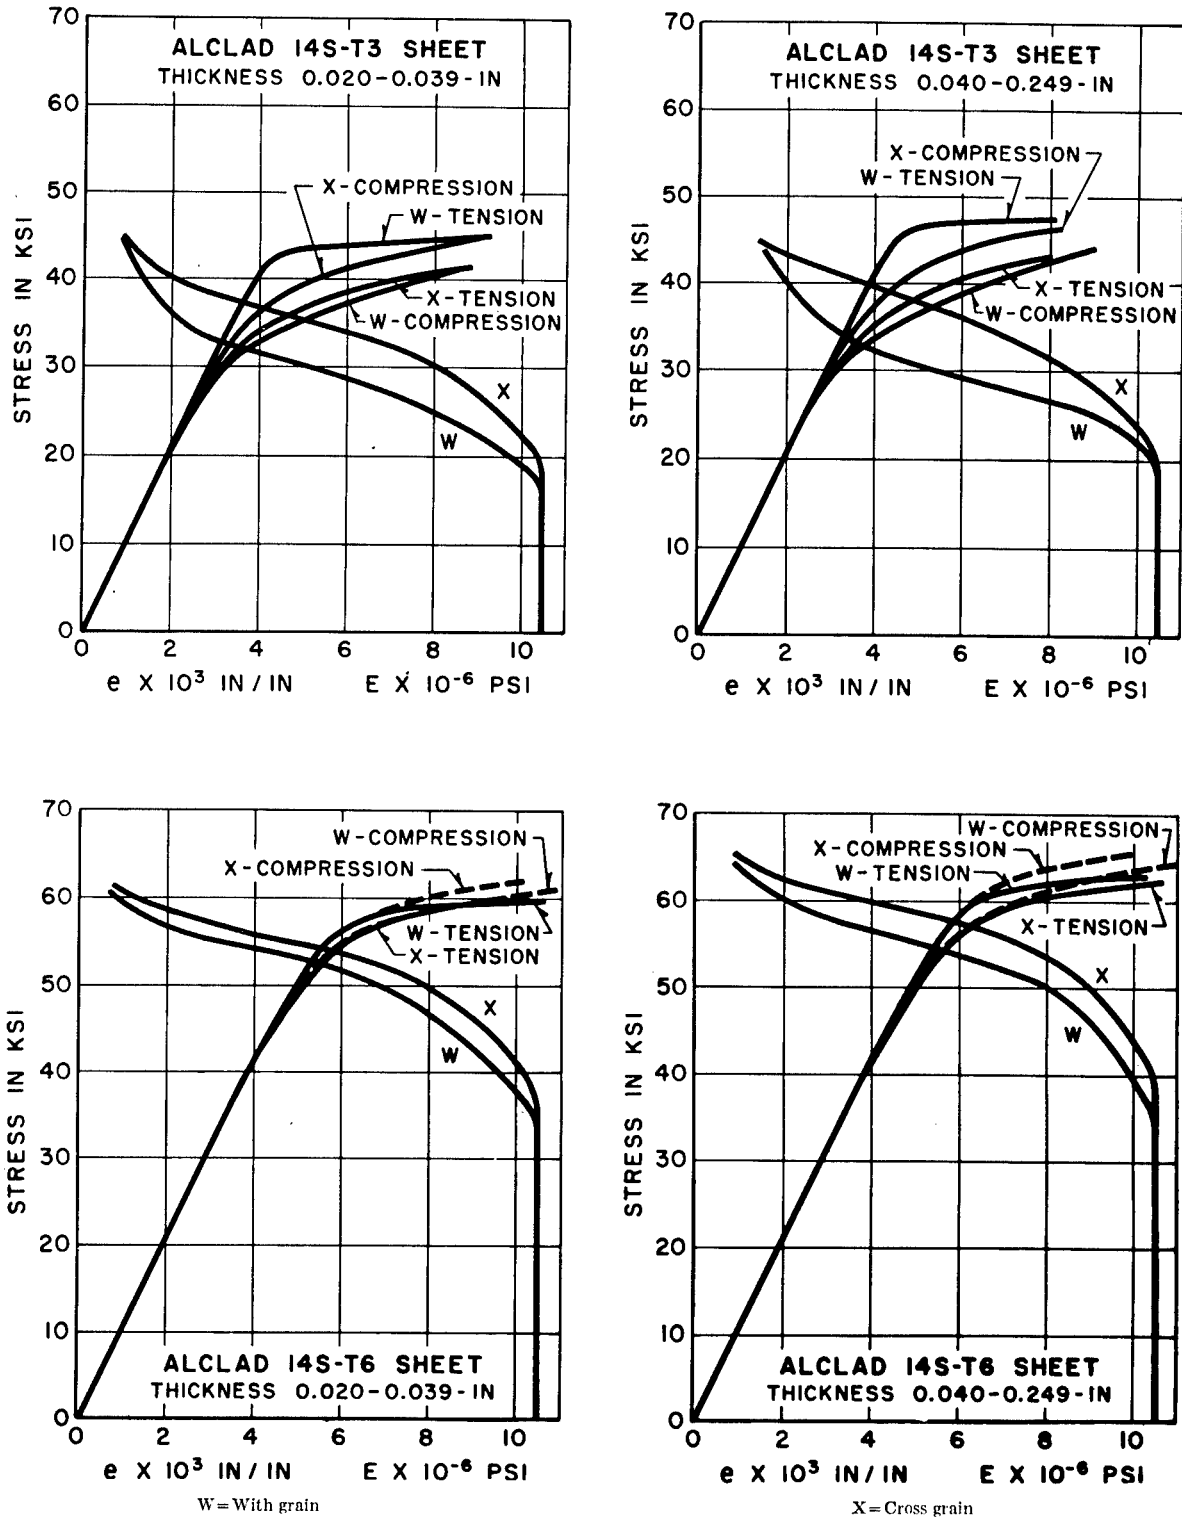


Figure 3.113 (b). Typical stress-strain and tangent compression modulus curves for 14S aluminum alloy sheet.

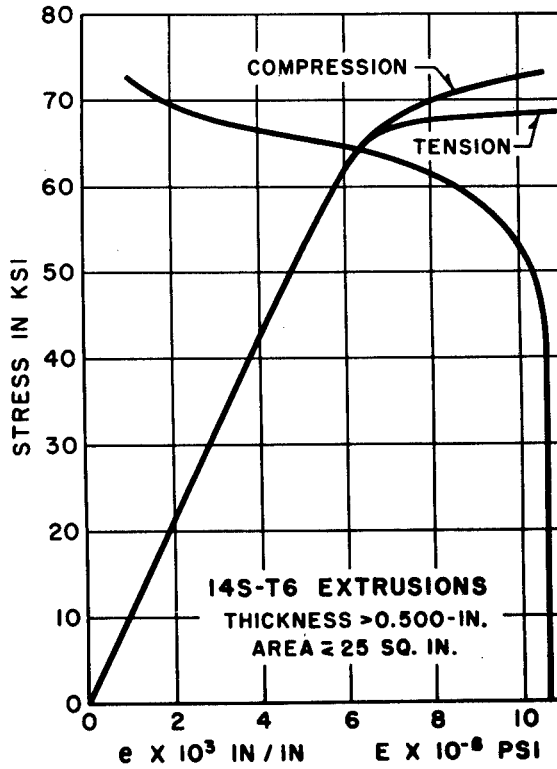
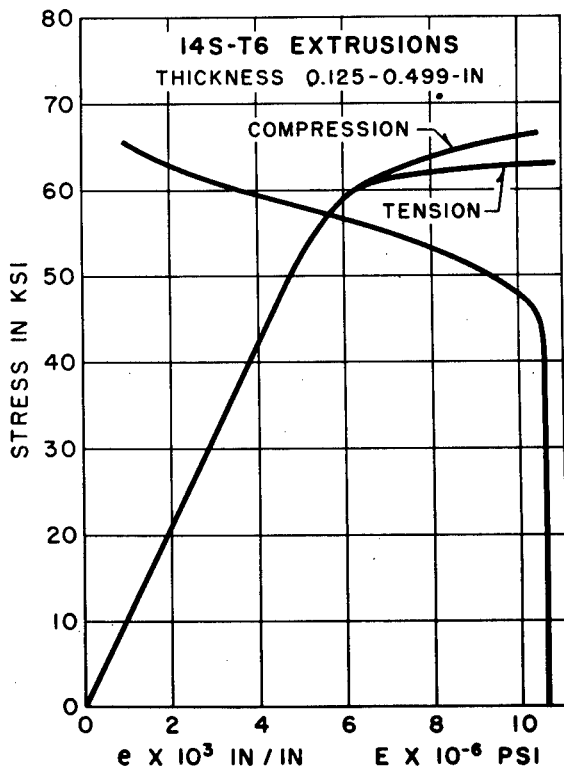
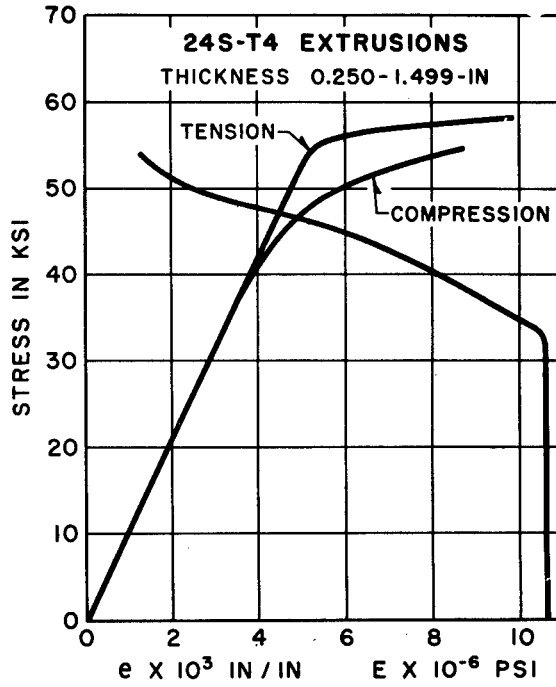
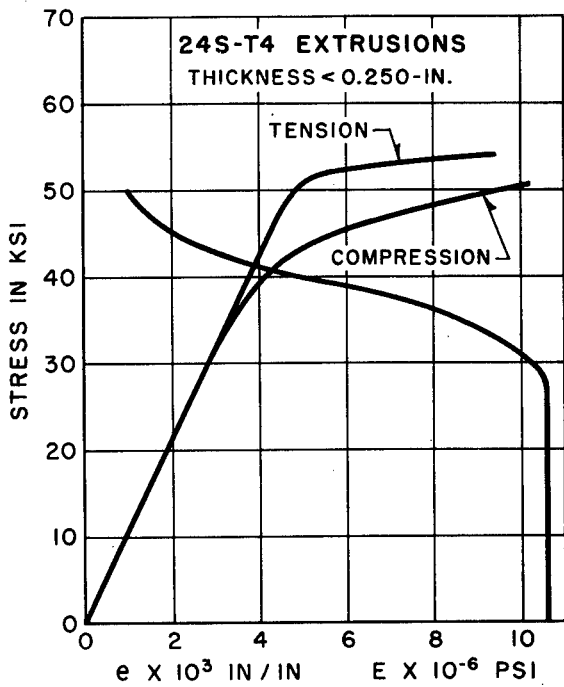


Figure 3.113 (c). Typical stress-strain and tangent modulus curves for 24S and 14S aluminum alloy extrusions.

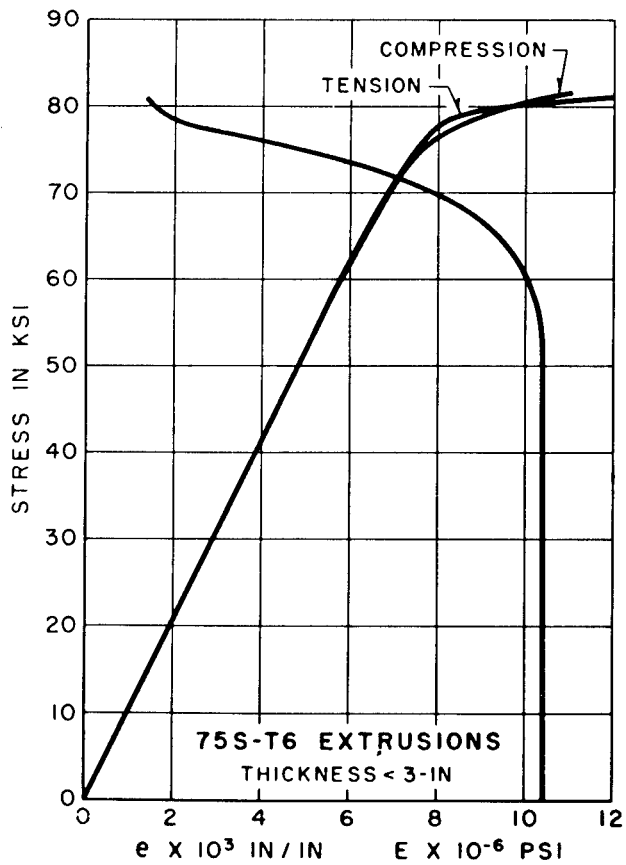
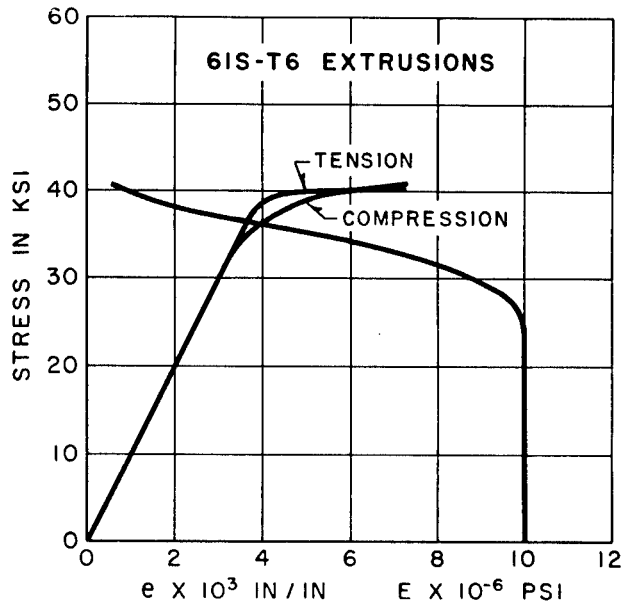


Figure 3.113 (d). Typical stress-strain and tangent modulus curves for 61S and 75S aluminum alloy extrusions.

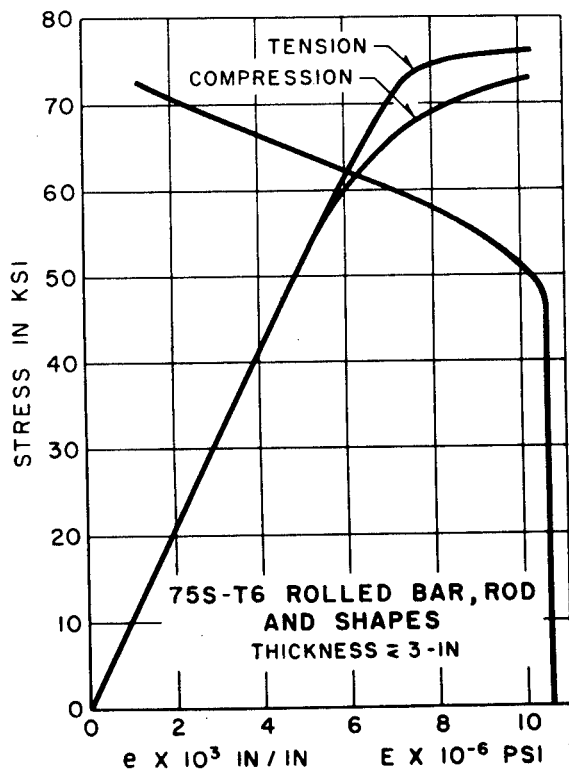
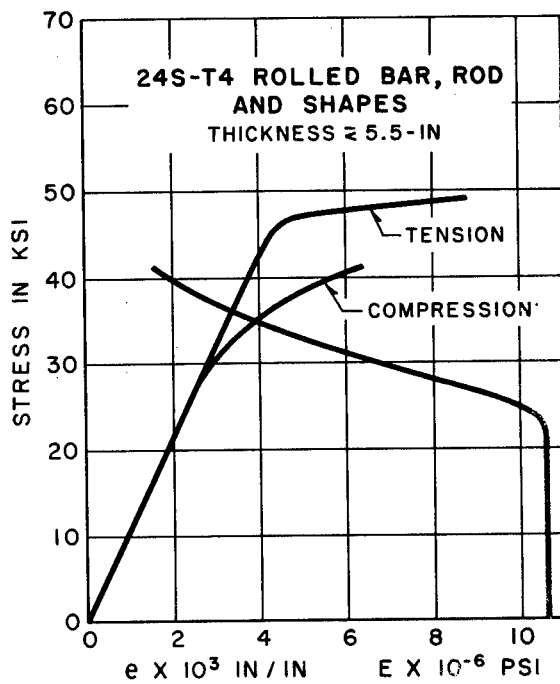
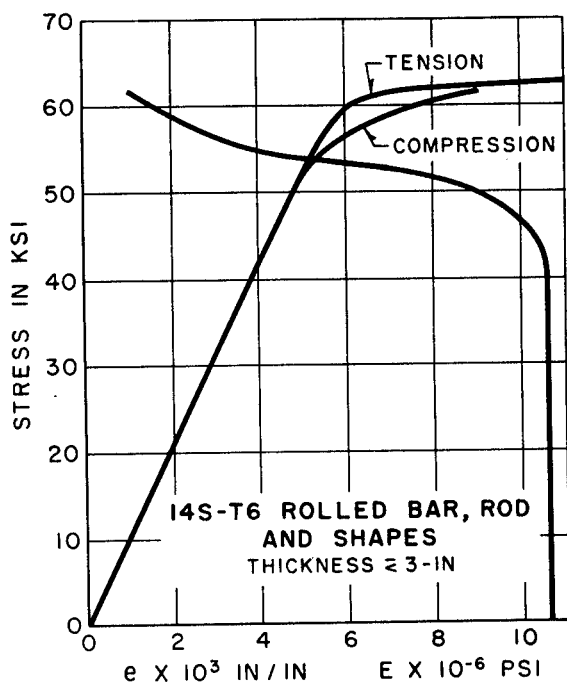


Figure 3.113 (e). Typical stress-strain and tangent modulus curves for 14S-T6, 24S-T4, and 75S-T6 aluminum alloy rolled bar, rod, and shapes.

Table 3.1211 (a). Acceptable Approximations of Effects of Low Temperatures on the Static Design Properties of Aluminum Alloys

Temperature (° F.)	Percent of room temperature ultimate strength for various material groups				Percent of room temperature yield strength for various material groups	
	Group TA	Group TB	Group TC	Group TD	Group YE	Group YF
75	100	100	100	100	100	100
0	103	103	103	101	101	102
-50	105	105	105	103	102	103
-100	111	109	108	105	103	106
-150	124	117	114	108	107	110
-200	137	127	121	112	110	116
-250	156	140	130	116	115	123
-300	179	156	139	118	118	130
-320	189	163	144	121	120	135

Tensile strength:

Group TA—2S-O, 3S-O, 53S-O, 61S-O (all products).

Group TB—2S-H14, 3S-H14 (all products).

Group TC—2S-H18, 3S-H18, 53S-T4, 53S-T6, 61S-T4, 61S-T6, 75S-O (all products).

Group TD—14S-T4, 14S-T6, 24S-T3, 24S-T4, 75S-T6 (all products).

Yield strength:

Group YE—2S-O, 2S-H14, 2S-H18, 3S-H14, 3S-H18, 14S-T6, 53S-T6, 61S-T6, 75S-O, 75S-T6 (all products).

Group YF—3S-O, 14S-T4, 24S-T3, 24S-T4, 53S-O, 53S-T4, 61S-O, 61S-T4 (all products).

Factors apply to clad as well as nonclad material.

<sup>1</sup> Values in group YE are somewhat high for all 14S-T6 products except extrusions; at -320° F., 112 percent should be used and for temperatures of -300 to 0° F. values should be correspondingly reduced.

Table 3.1211 (b). Effect of Various Temperatures on the Modulus of Elasticity of Aluminum Alloys

Temperature (° F.)	Approximate value of modulus in terms of modulus at 75° F. (percent)
-320	112
-112	107
-18	102
75	100
212	98
300	95
400	90
500	80

Table 3.1212. Flexure Type Fatigue Data

[Values given were obtained by testing 0.5 inch diameter polished specimens in flexure in Krouse type plate fatigue machines and represent the extreme fiber stresses which such specimens will withstand in completely reversed stressing]

[All values in kips per square inch]

Alloy and temper	Approximate maximum stress which material will withstand for given number of cycles				
	1,000	5,000	50,000	500,000	10,000,000
Room temperature					
2S-H14	30	24.5	17.5	14	11
24S-T4	80	63	44	35	26
61S-T6	64	52	34	27	20
75S-T6	92	75	52	34	31
-108° F.					
2S-H14	35	29	21.5	17.5	-----
24S-T4	85	71	51	39	31
61S-T6	70	57	38	-----	-----
75S-T6	94	78	56	40	-----
-320° F.					
2S-H14	40.5	35.5	29.5	-----	-----
24S-T4	98	86	71	53	-----
61S-T6	80	68	52	40	-----
75S-T6	108	96	78	-----	-----

### 3.122 Elevated temperature

3.1221 General. The data shown in figures 3.1221 (a) and (b) for short-time tests are based on continuous heating but are considered applicable to intermittent heating when the total time at temperature is the same. The data shown in figures 3.1221 (c) through (l) are also based on continuous heating and loading but must be used with discretion for intermittent heating and loading as deformations may be larger and failure times shorter for the latter conditions. The data included in the tables are based on specimens heated in air with no added corrosive agents. Consideration must be given to the fact that materials in service may be exposed to more corrosive atmospheres over longer periods of time under temperature variations.

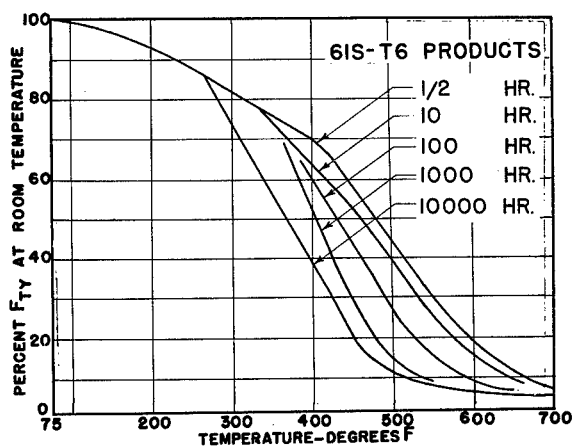
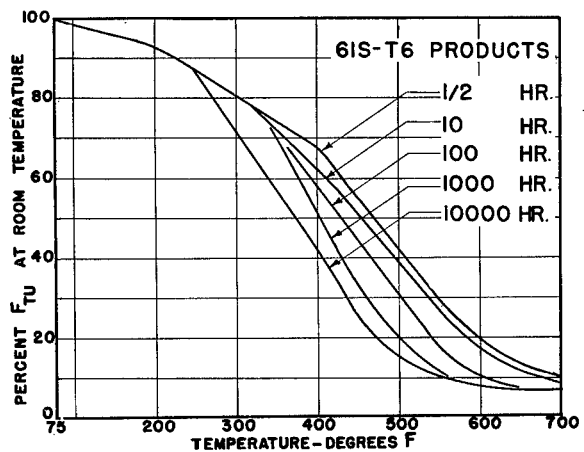
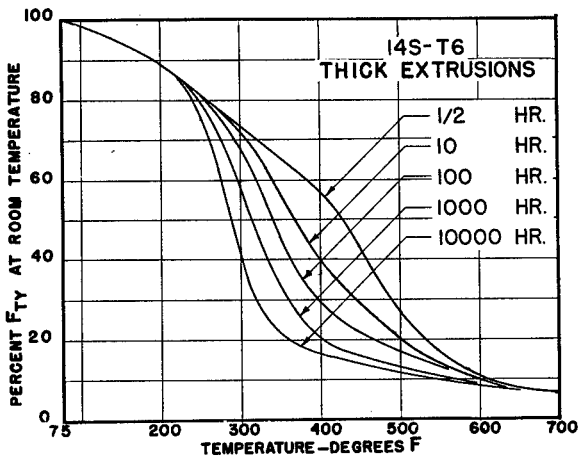
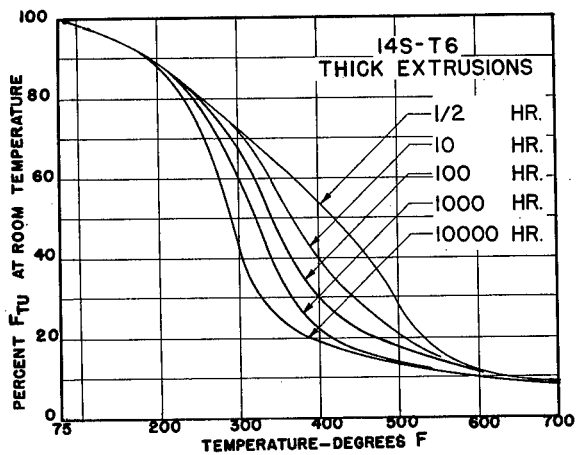
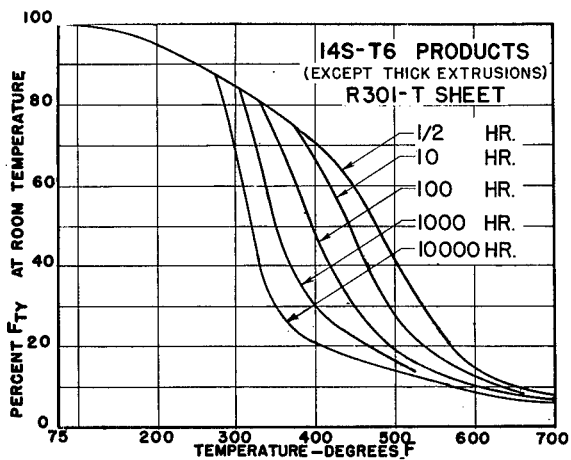
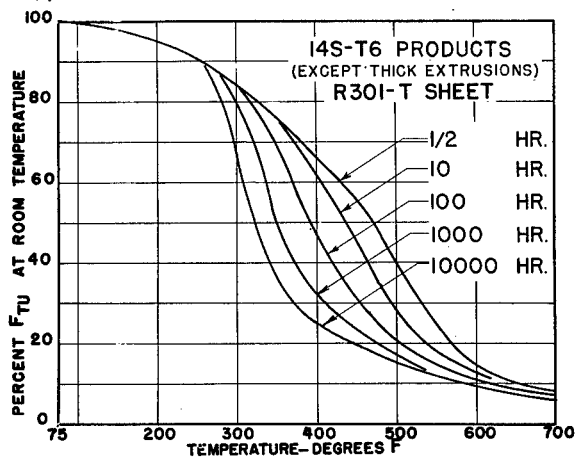


Figure 3.1221 (a). Aluminum alloy tensile properties at elevated temperatures.

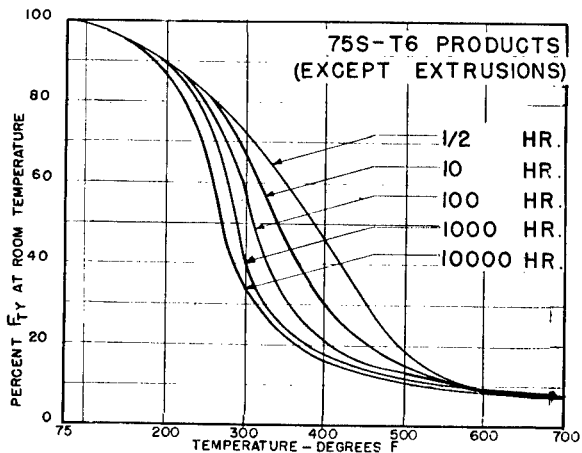
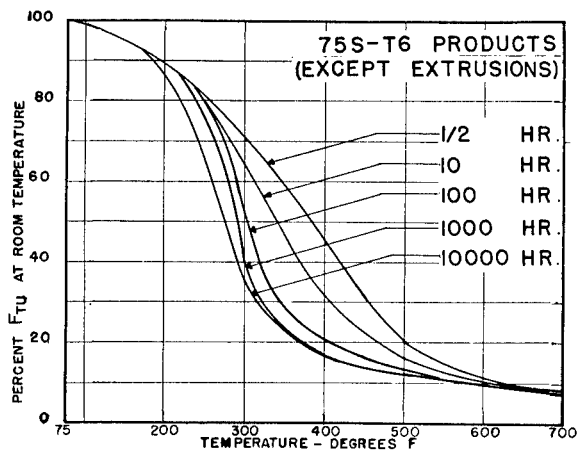
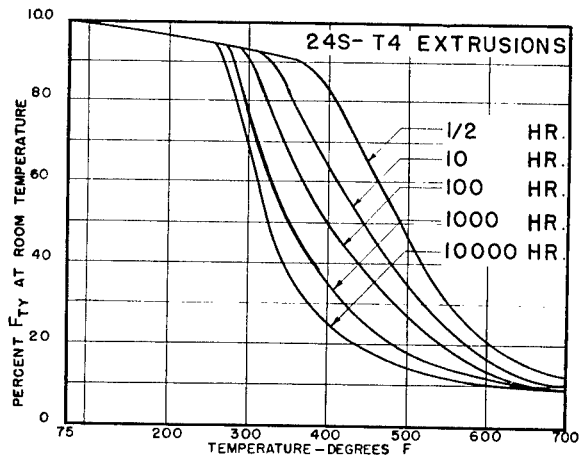
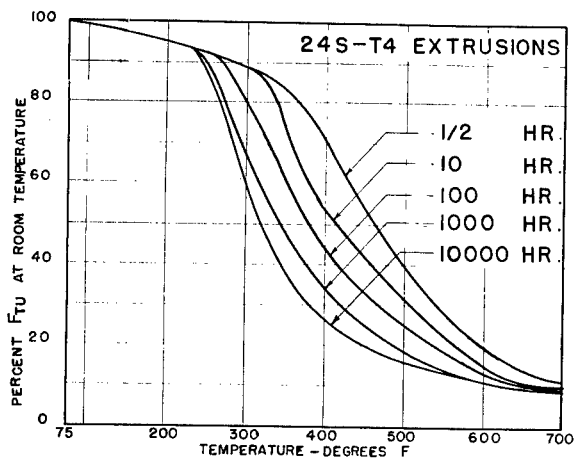
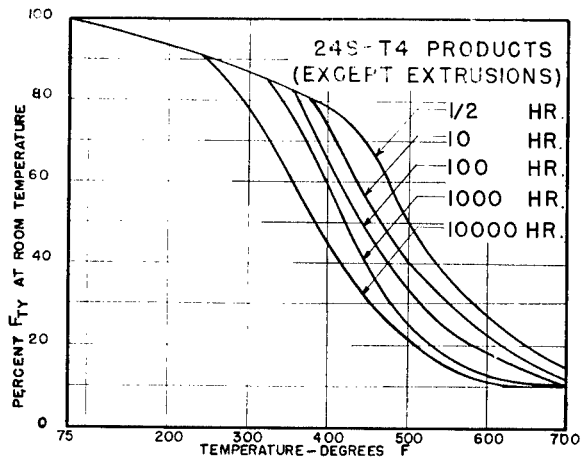
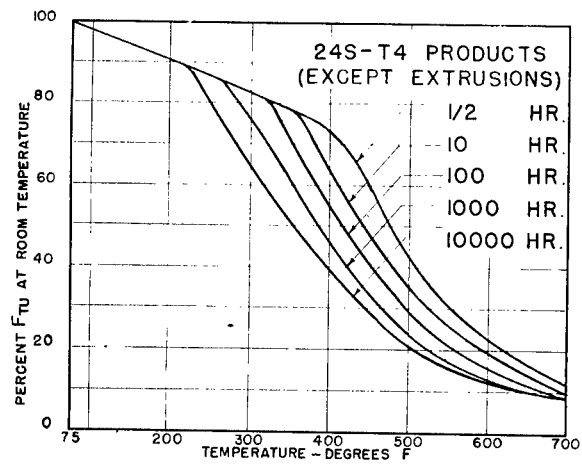


Figure 3.1221 (b). Aluminum alloy tensile properties at elevated temperatures.



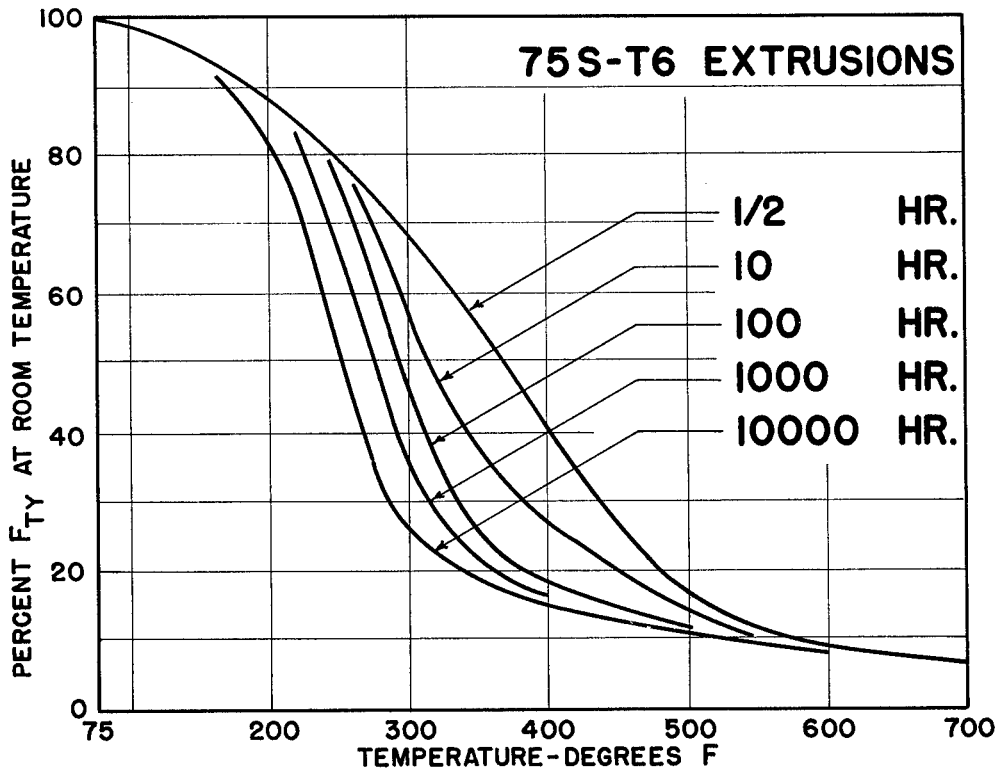
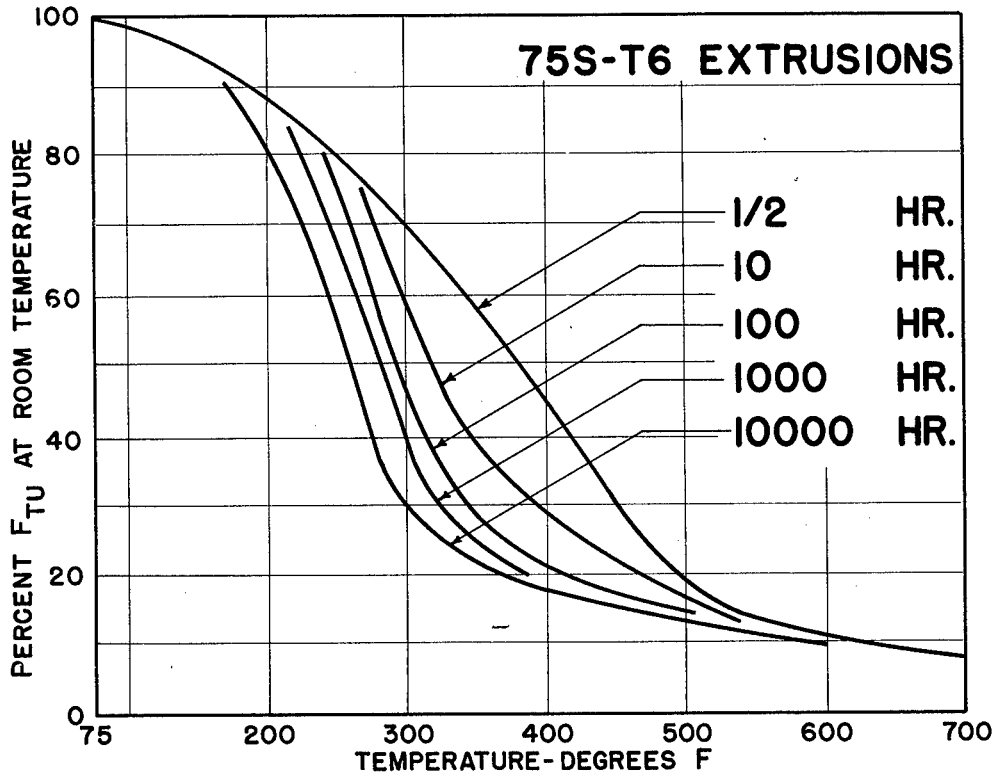


Figure 3.1221 (c). Aluminum alloy tensile properties at elevated temperatures.


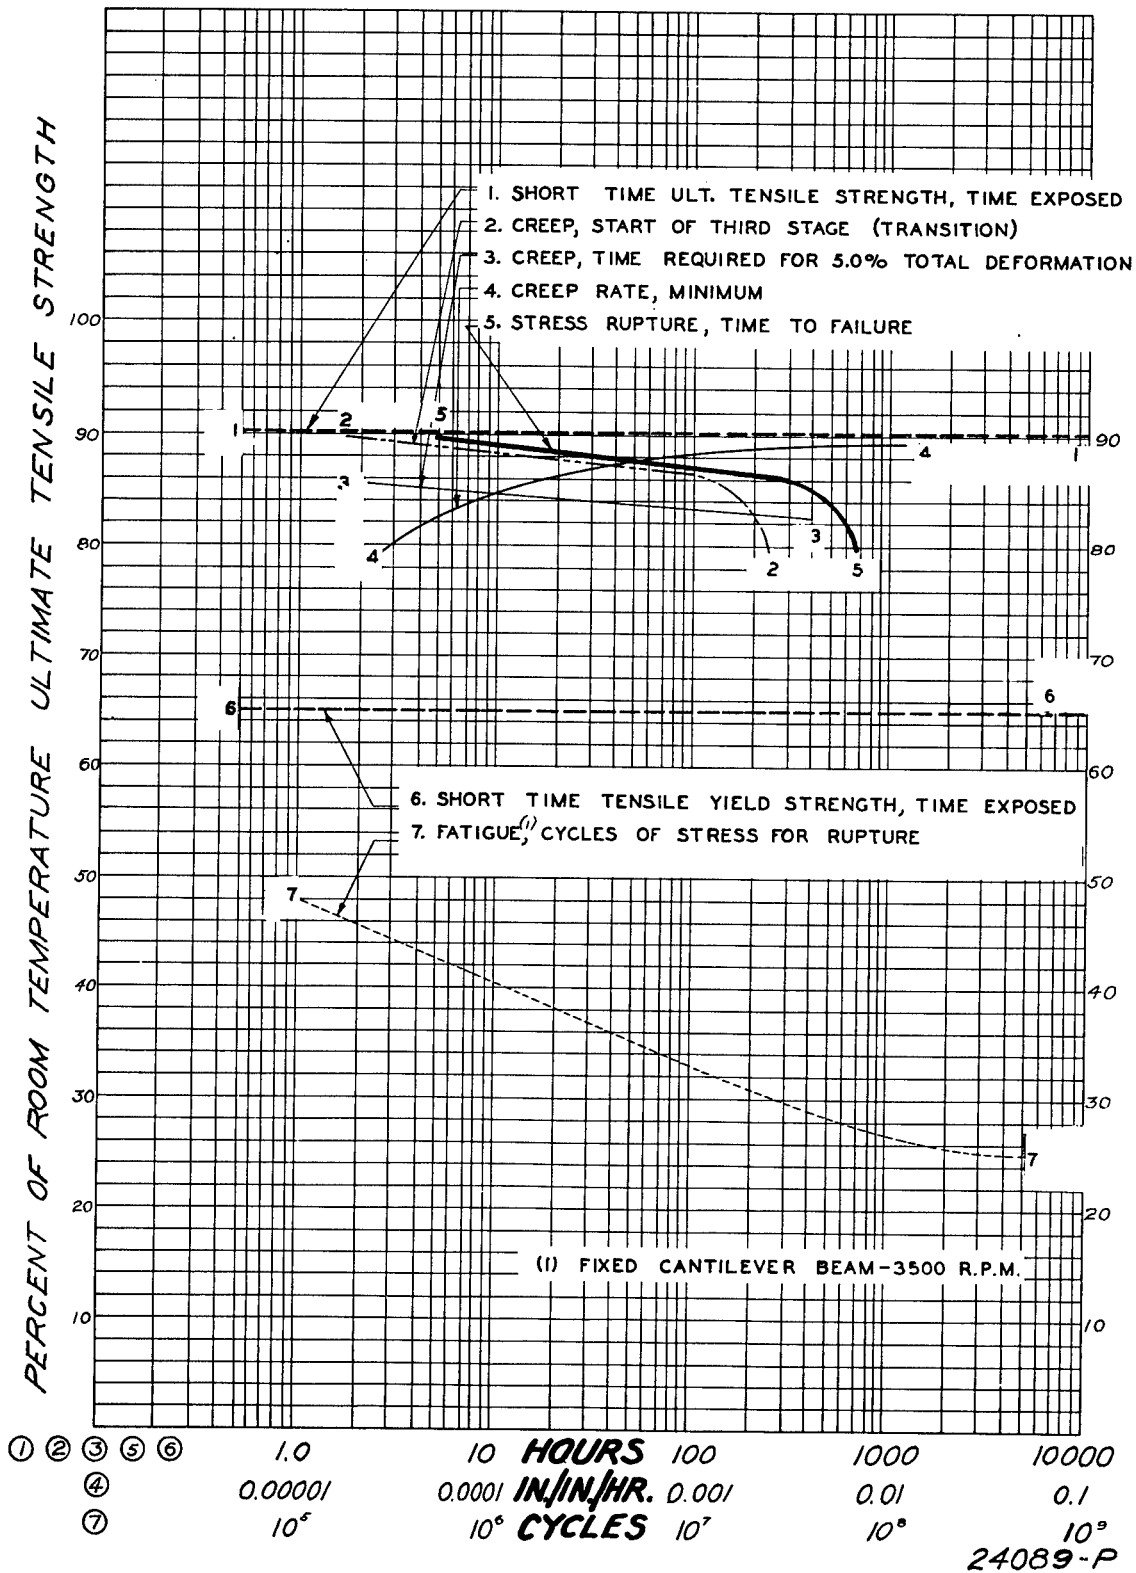



Figure 3.1221 (d). Elevated temperature properties of wrought 24S-T3 aluminum alloy at 211° F.

PERCENT OF ROOM TEMPERATURE ULTIMATE TENSILE STRENGTH

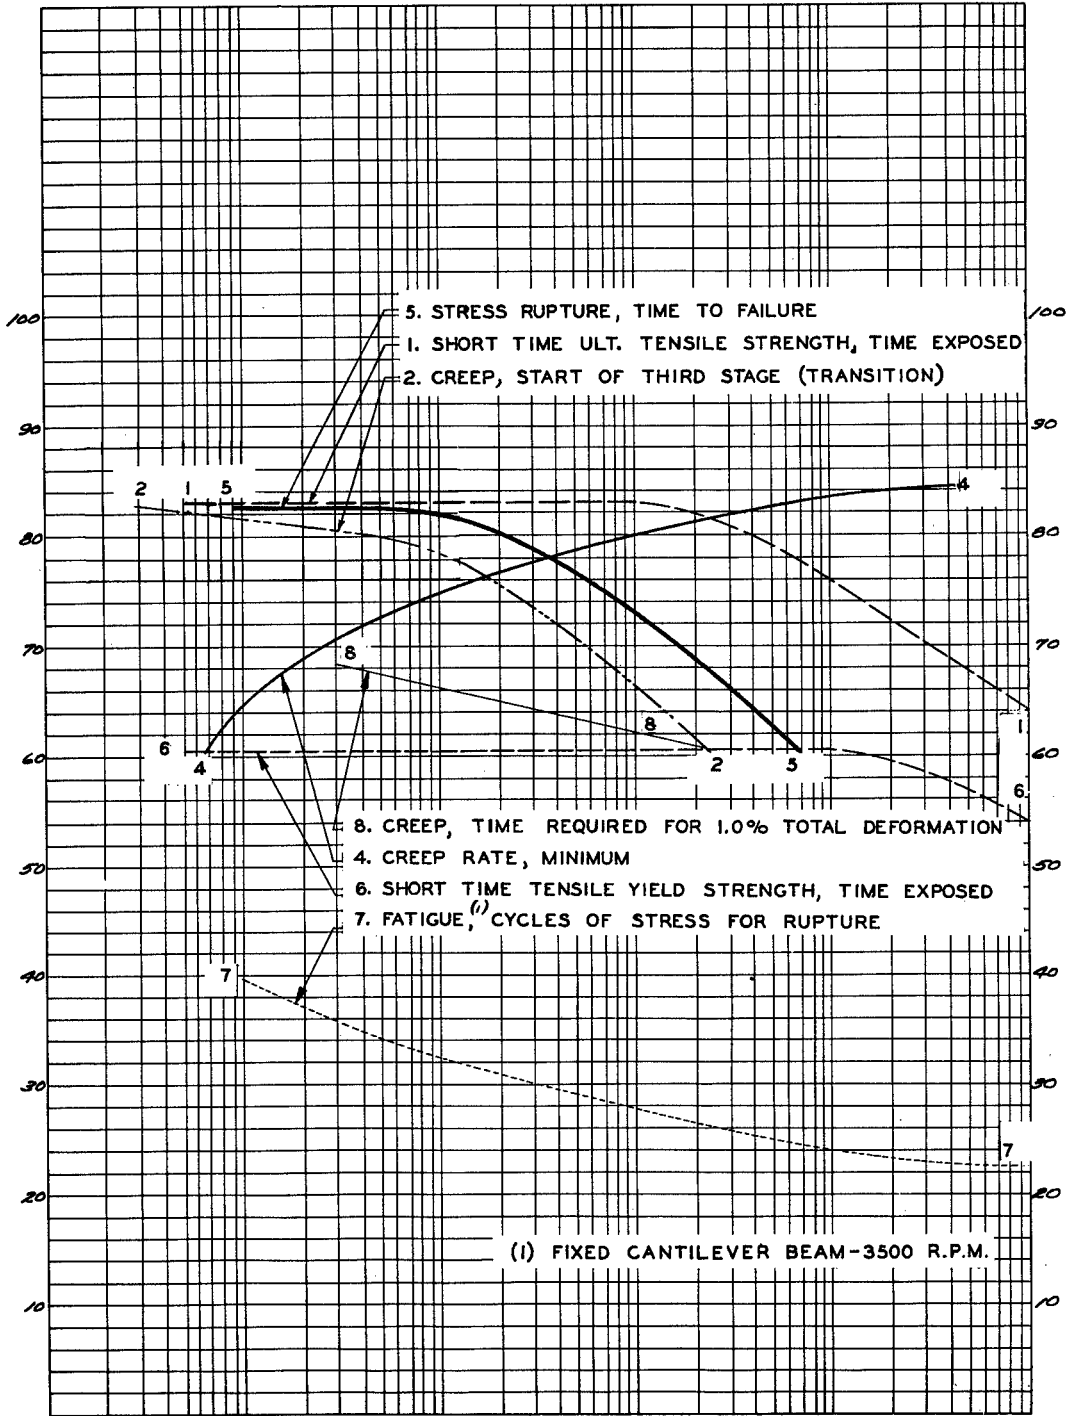

①	②	⑤	⑥	⑧	1.0	10	HOURS	100	1000	10000
④					0.00001	0.0001	IN./IN./HR.	0.001	0.01	0.1
⑦					10 <sup>5</sup>	10 <sup>6</sup>	CYCLES	10 <sup>7</sup>	10 <sup>8</sup>	10 <sup>9</sup>

24090-P

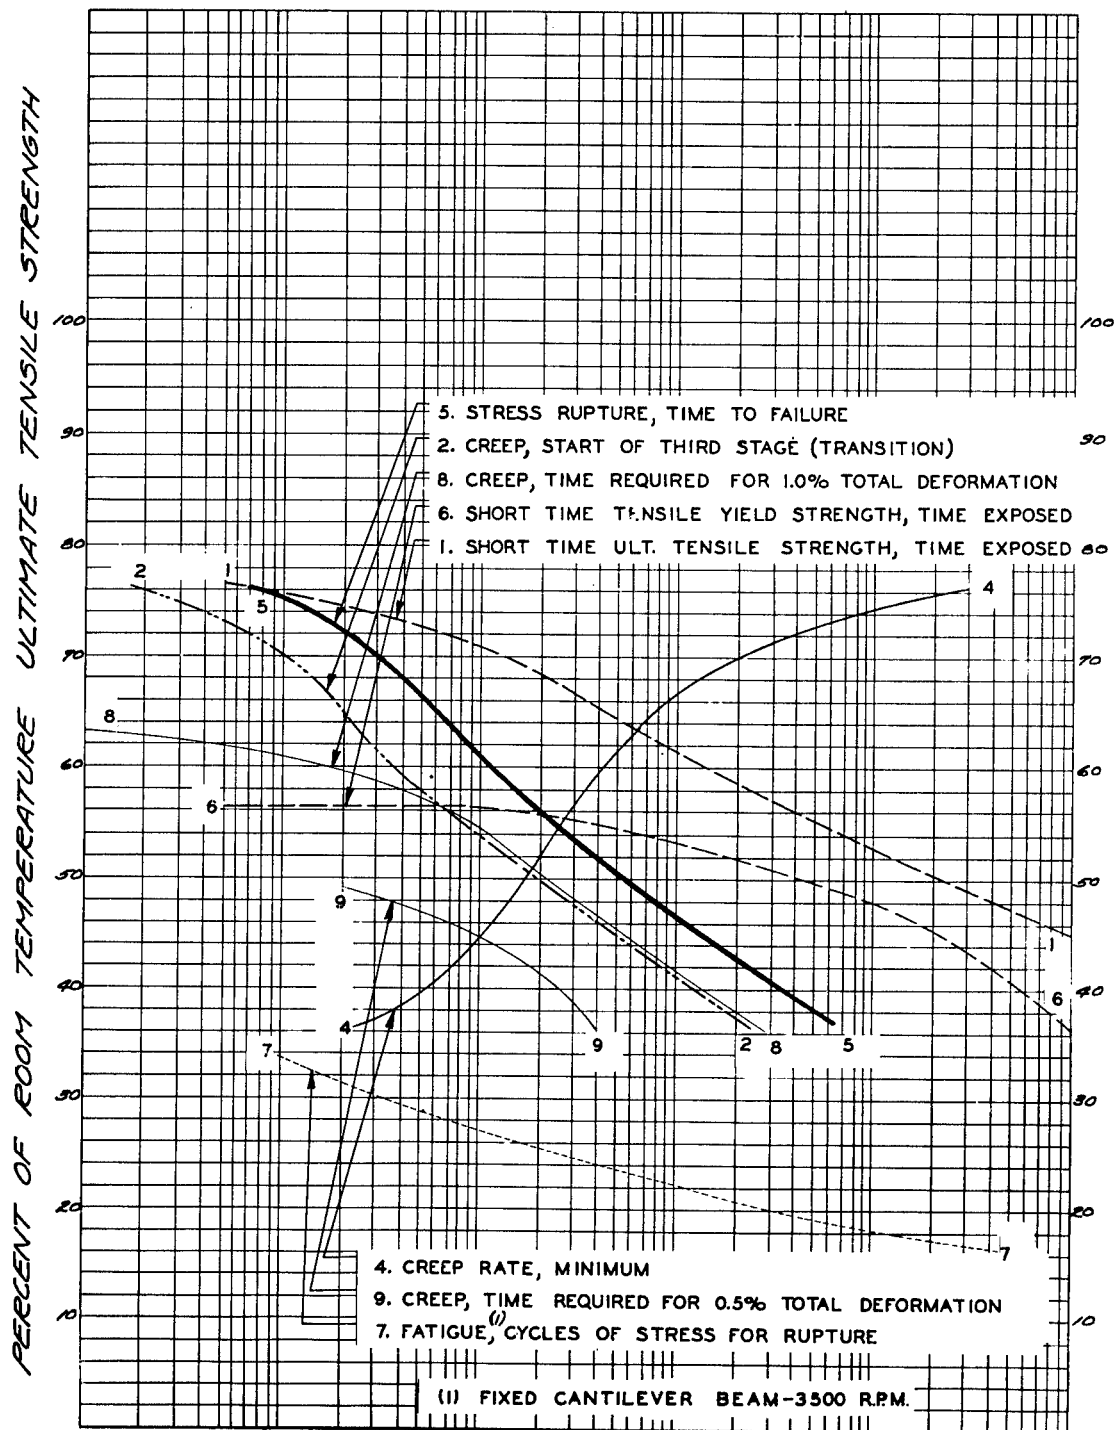


①	②	⑤	⑥	⑧	⑨	10	10 HOURS	100	1000	10000
④						0.00001	0.0001 IN./IN./HR.	0.001	0.01	0.1
⑦						10 <sup>5</sup>	10 <sup>6</sup> CYCLES	10 <sup>7</sup>	10 <sup>8</sup>	10 <sup>9</sup>

24091-P

Figure 3.1221 (f). Elevated temperature properties of wrought 24S-T3 aluminum alloy at 375° F.

PERCENT OF ROOM TEMPERATURE ULTIMATE TENSILE STRENGTH

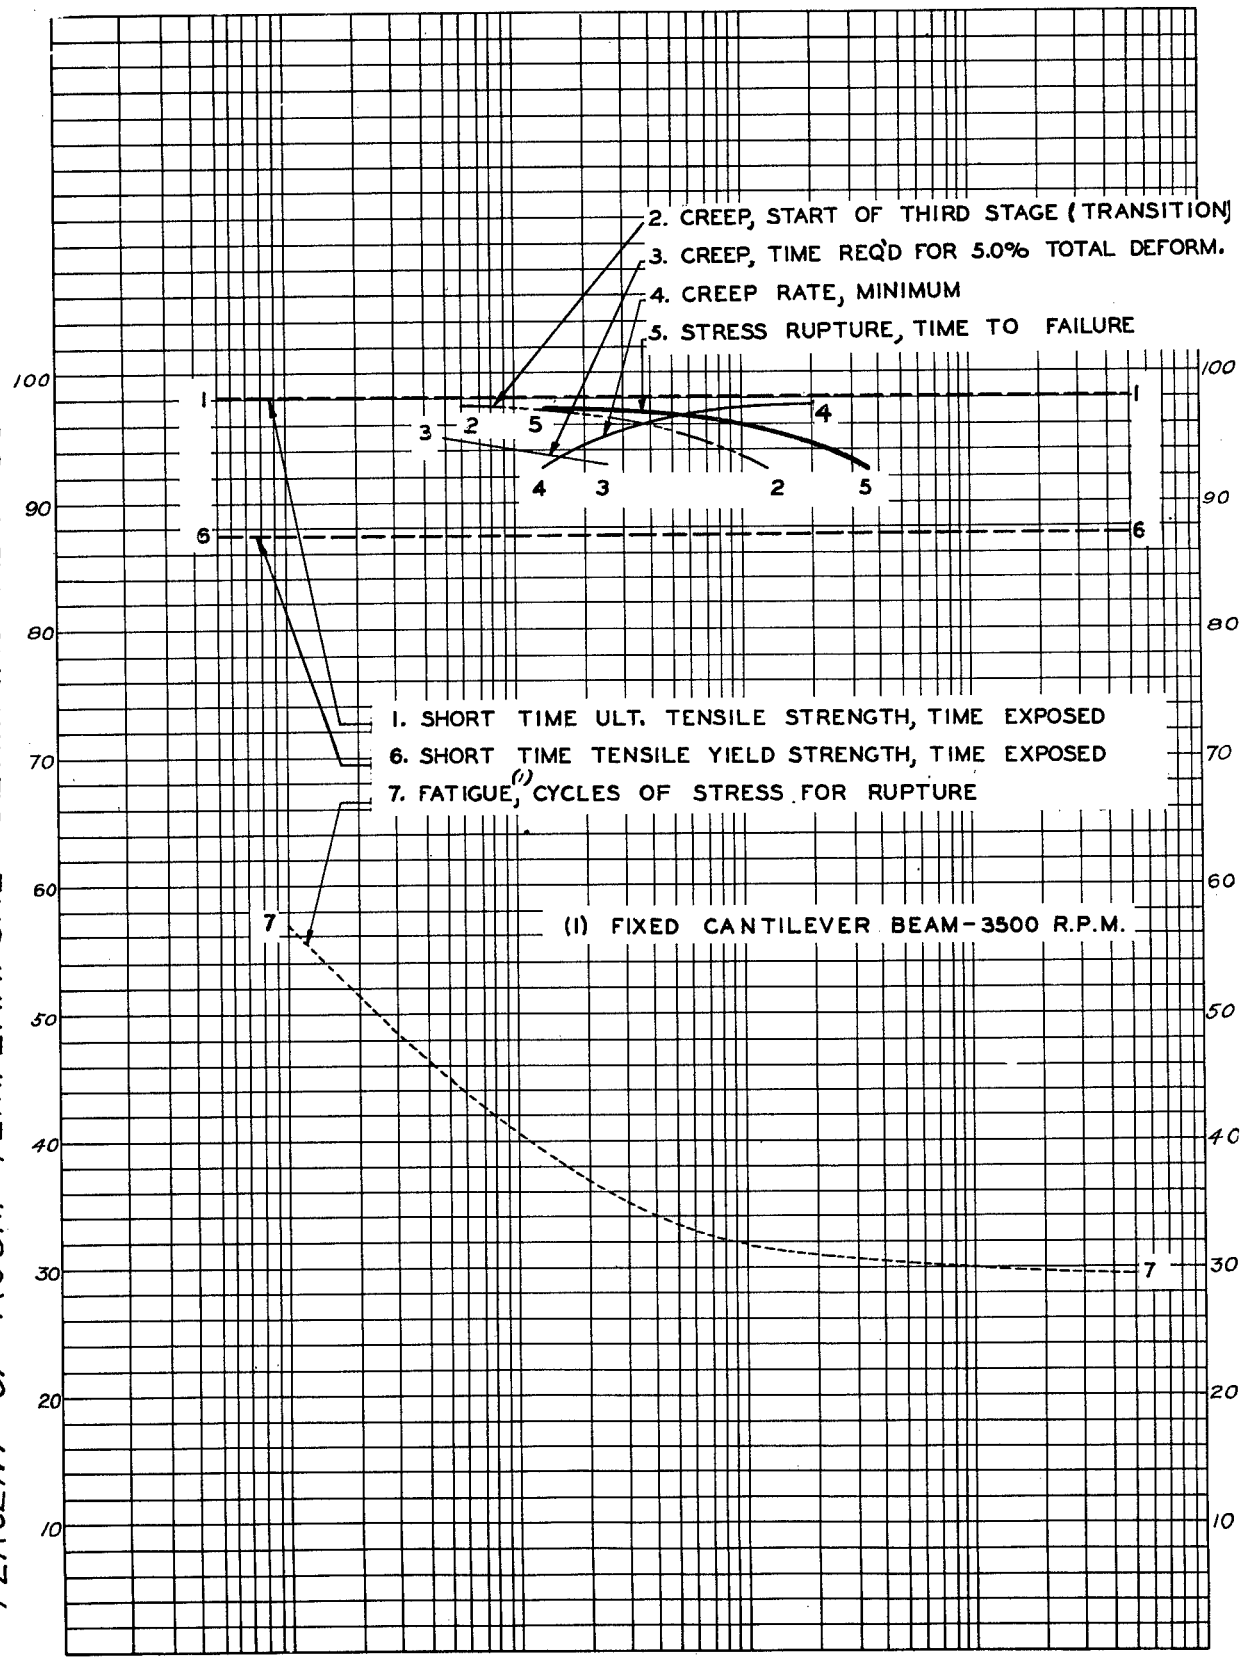

- 2. CREEP, START OF THIRD STAGE (TRANSITION)
- 3. CREEP, TIME REQ'D FOR 5.0% TOTAL DEFORM.
- 4. CREEP RATE, MINIMUM
- 5. STRESS RUPTURE, TIME TO FAILURE


- 1. SHORT TIME ULT. TENSILE STRENGTH, TIME EXPOSED
- 6. SHORT TIME TENSILE YIELD STRENGTH, TIME EXPOSED
- 7. FATIGUE, CYCLES OF STRESS FOR RUPTURE

(I) FIXED CANTILEVER BEAM-3500 R.P.M.

①	②	③	④	⑤	⑥	⑦
	1.0	10	100	1000	10000	
	0.00001	0.0001	0.001	0.01	0.1	
	10 <sup>5</sup>	10 <sup>6</sup>	10 <sup>7</sup>	10 <sup>8</sup>	10 <sup>9</sup>	

24092-P

PERCENT OF ROOM TEMPERATURE ULTIMATE TENSILE STRENGTH

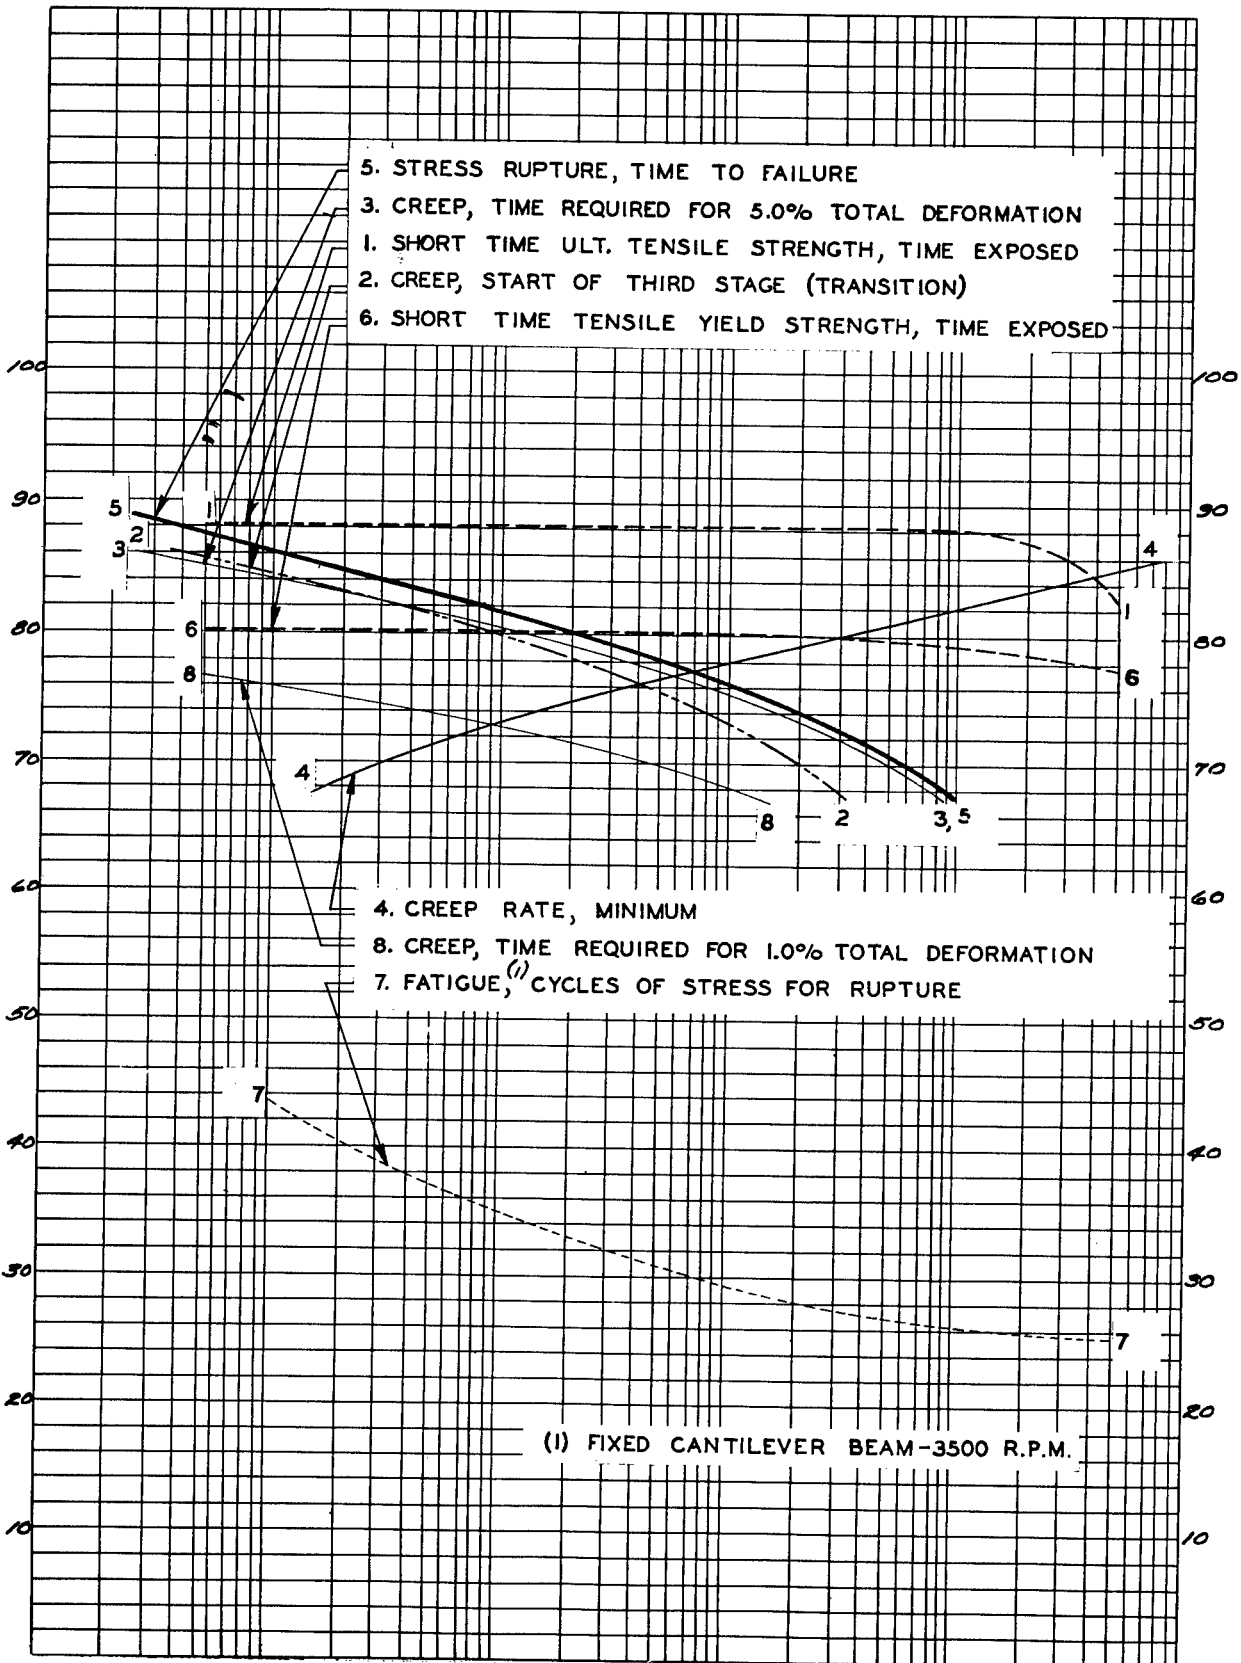

①②③⑤⑥⑧	1.0	10	100	1000	10000
④	0.00001	0.0001	0.001	0.01	0.1
⑦	10 <sup>5</sup>	10 <sup>6</sup>	10 <sup>7</sup>	10 <sup>8</sup>	10 <sup>9</sup>


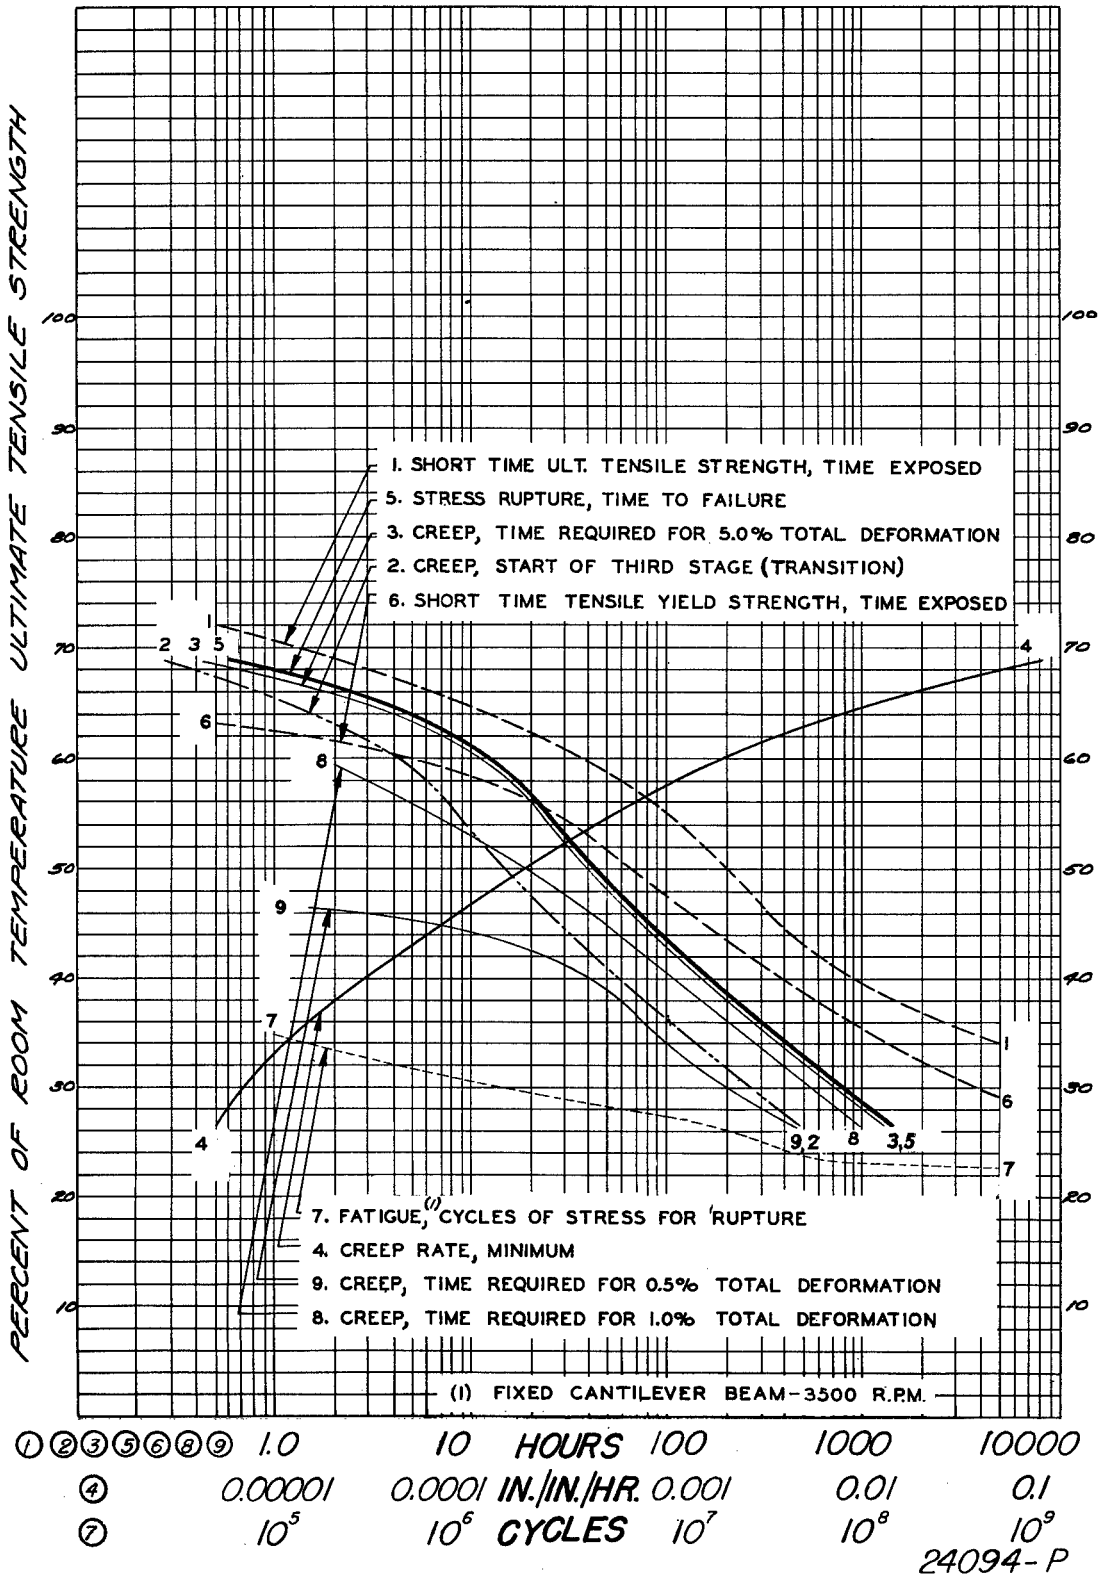


Figure 3.1221 (i). Elevated temperature properties of wrought 75S-T6 aluminum alloy at 300° F.

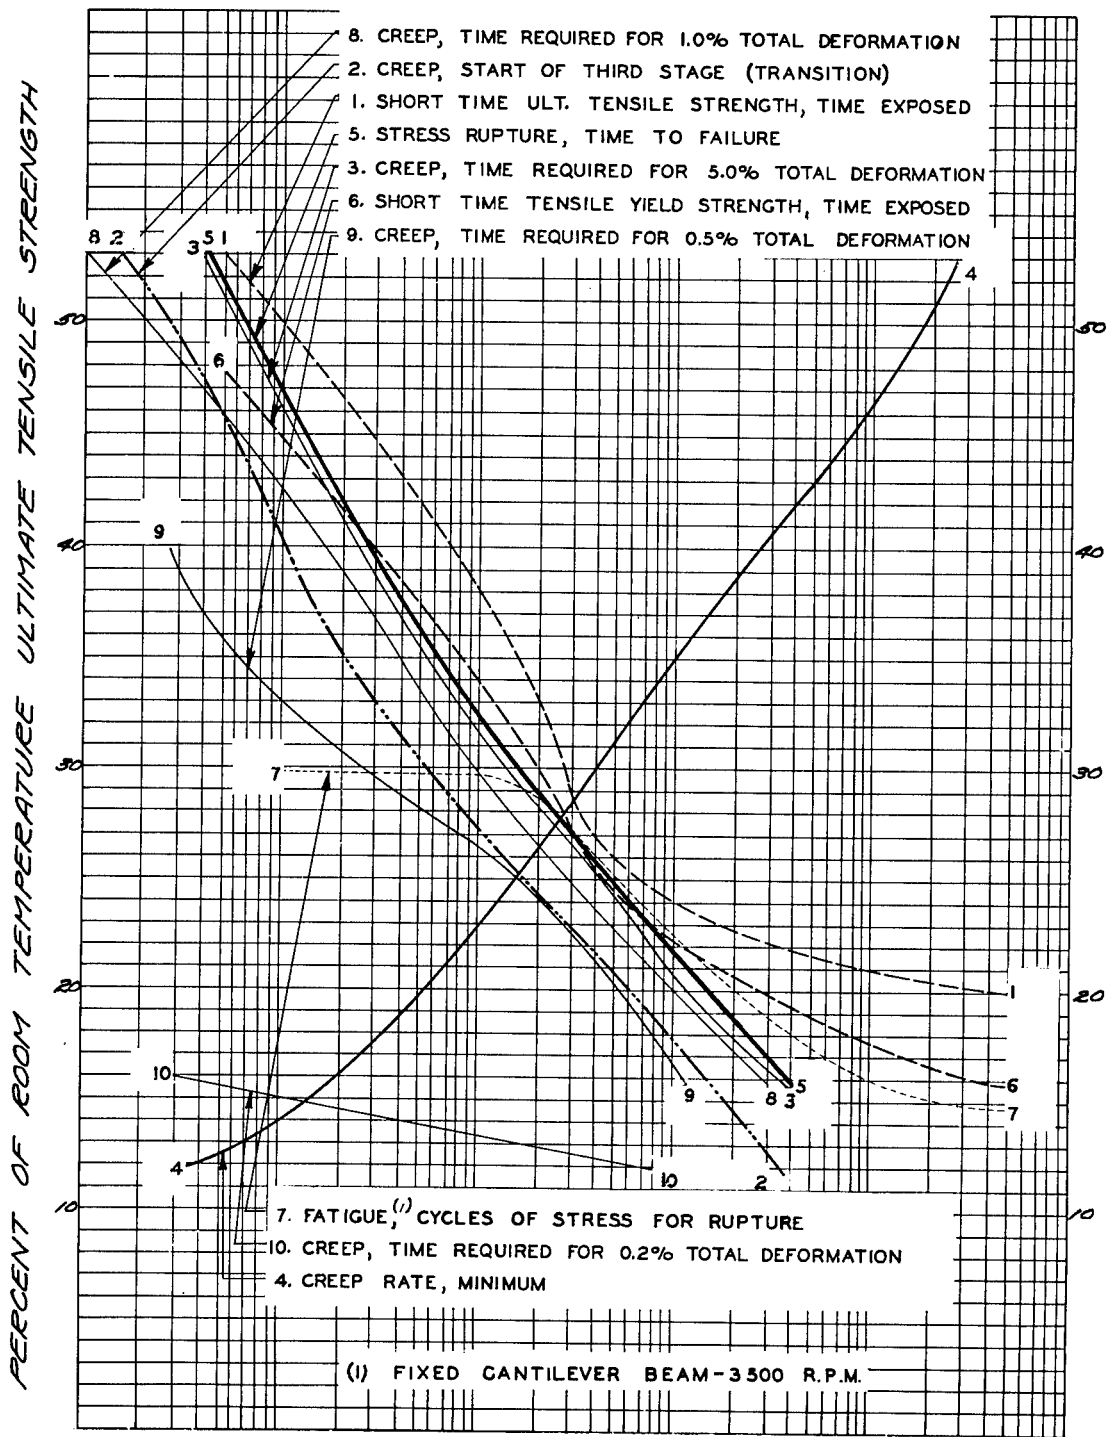

①	②	③	④	⑤	⑥	⑦	⑧	⑨	⑩	1.0	10	HOURS	100	1000	10000
④										0.00001	0.0001	IN./IN./HR.	0.001	0.01	0.1
⑦										10 <sup>5</sup>	10 <sup>6</sup>	CYCLES	10 <sup>7</sup>	10 <sup>8</sup>	10 <sup>9</sup>

24095-P

Figure 3.1221 (j). Elevated temperature properties of wrought 75S-T6 aluminum alloy at 375° F.



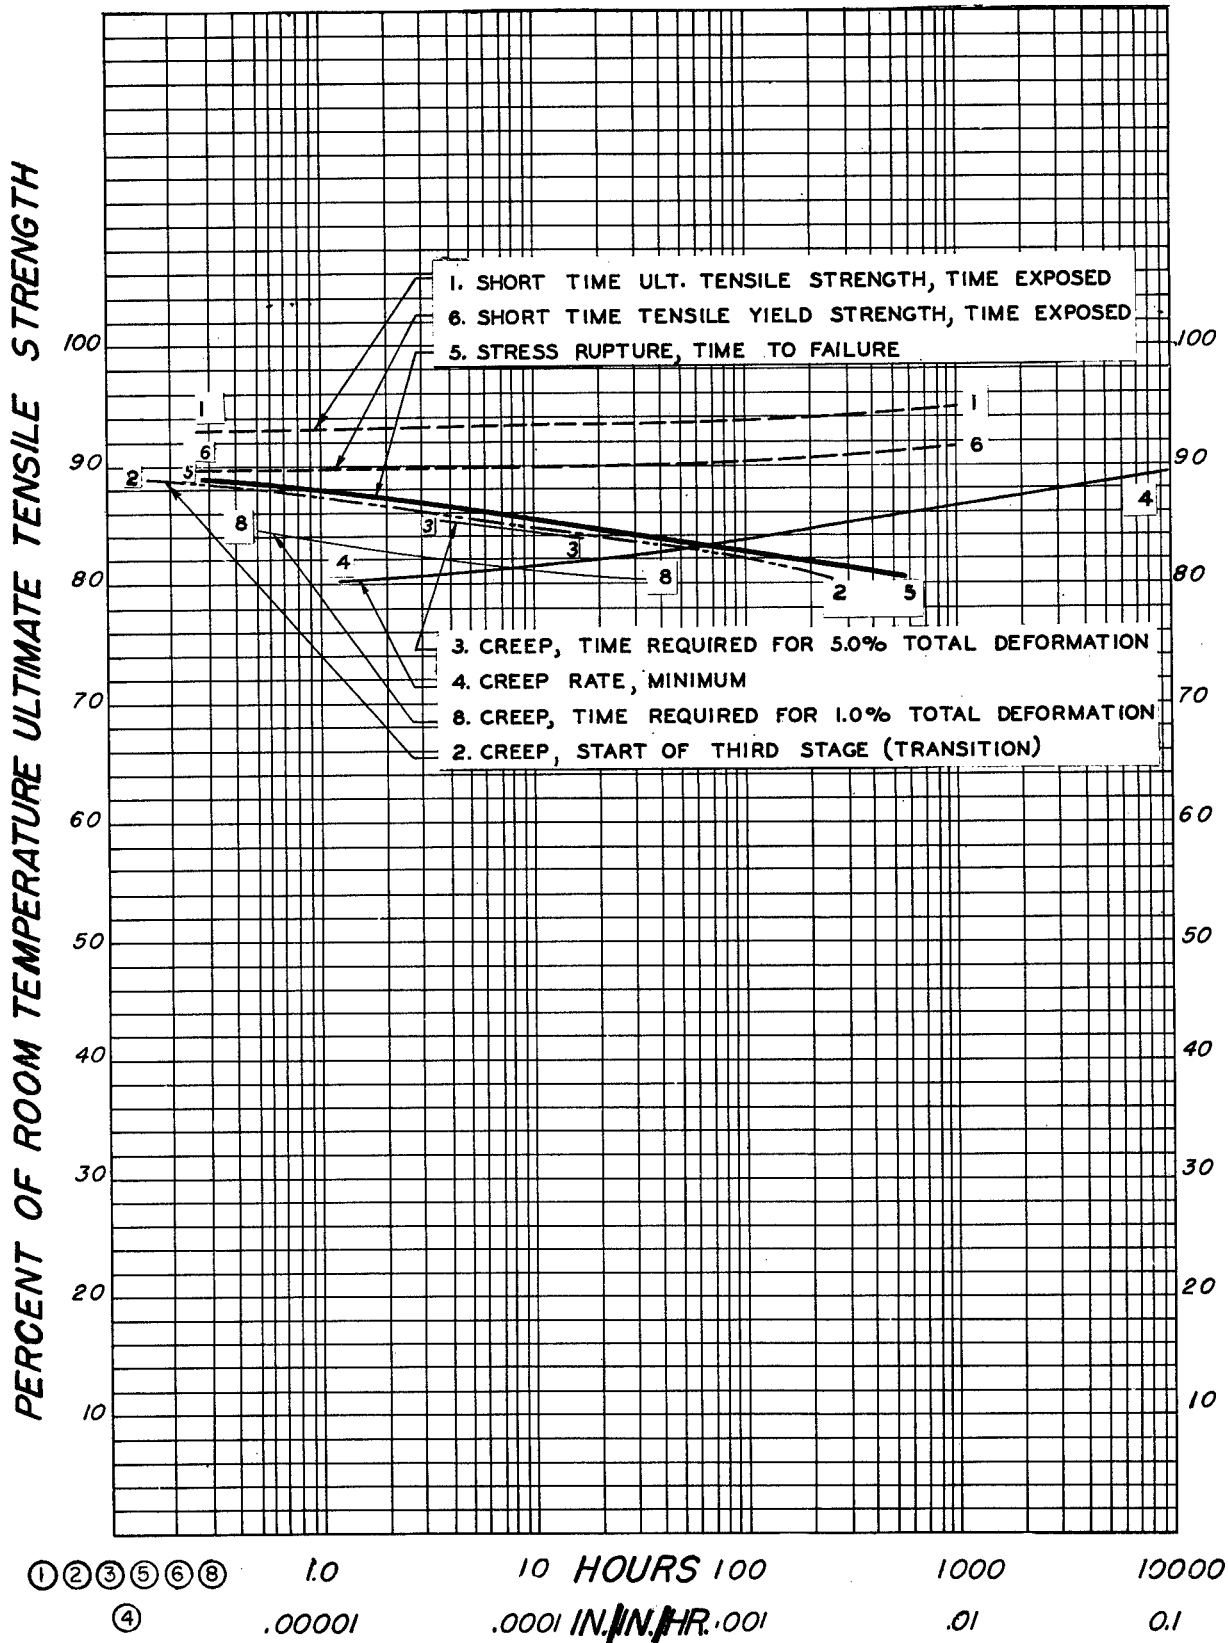


Figure 3.1221 (k). Elevated temperature properties of clad 24S-T86 aluminum alloy (heat treated, cold worked, and aged) at 211° F.


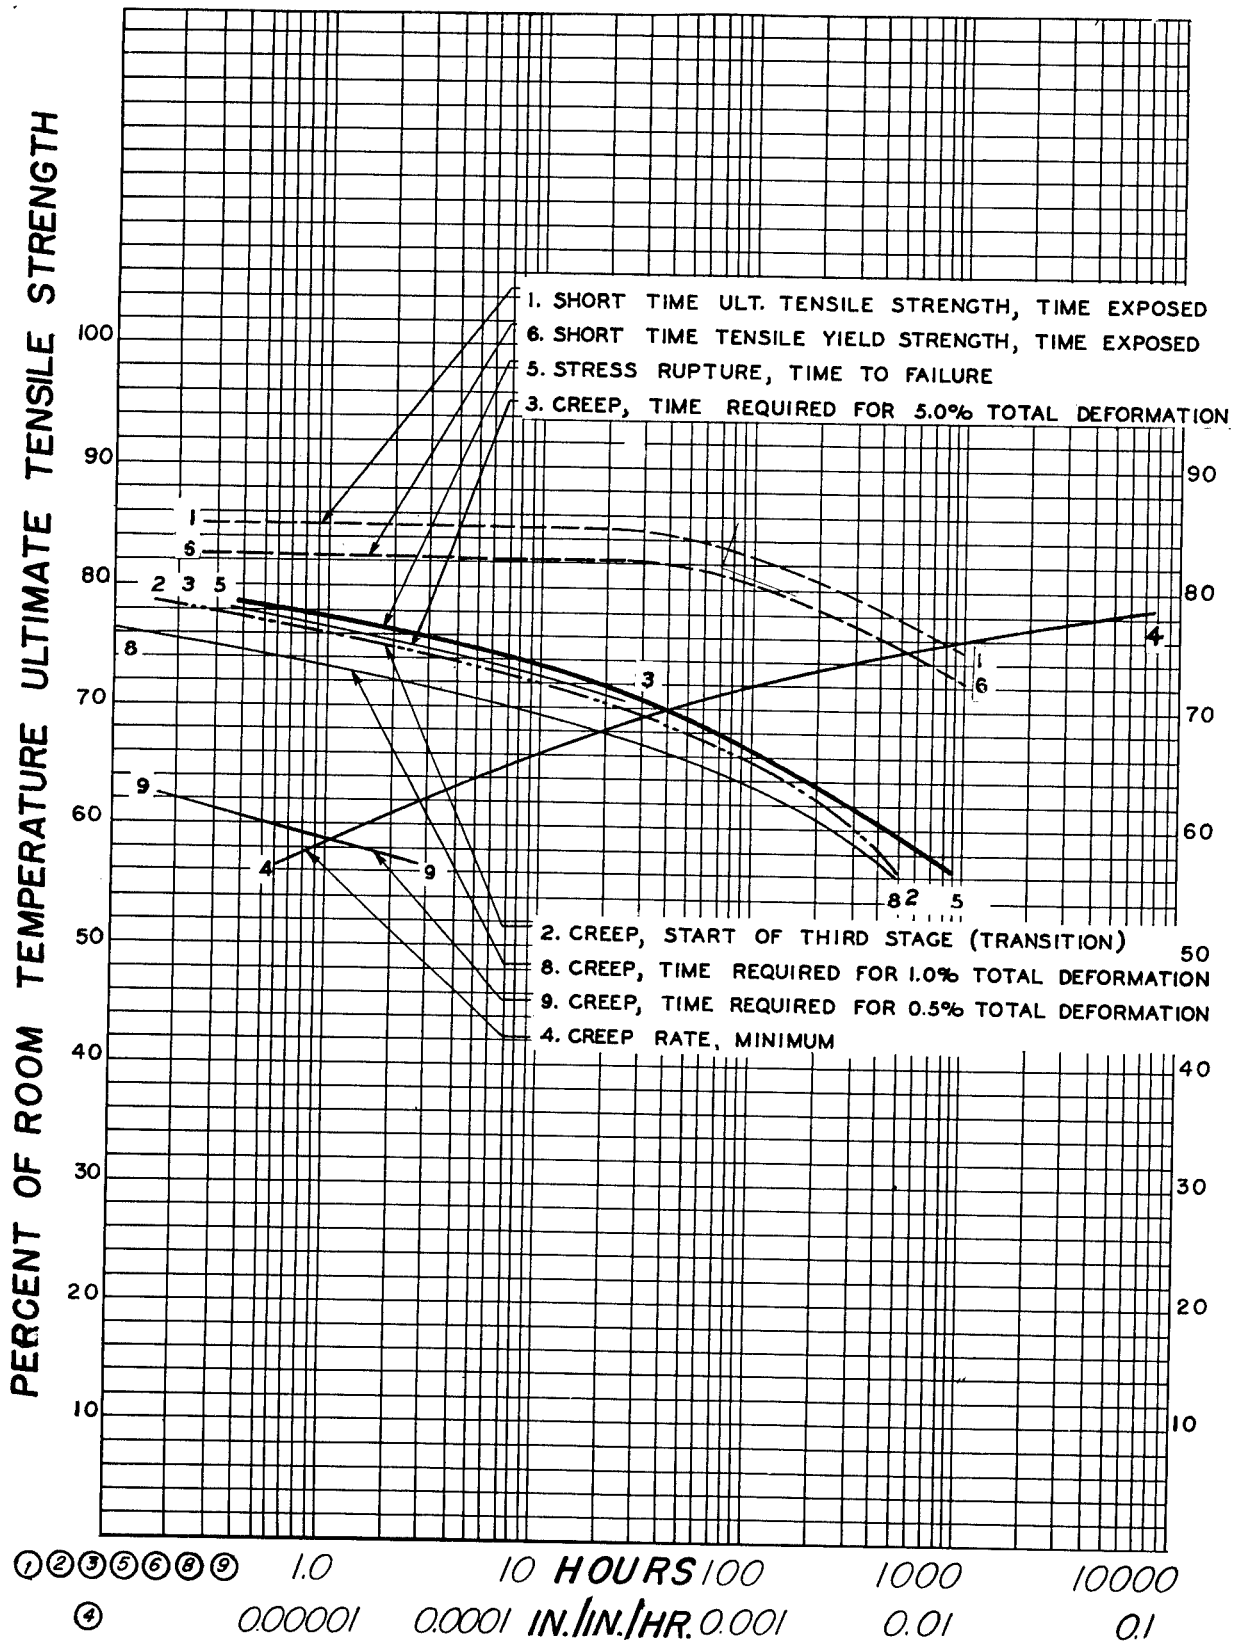


Figure 3.1221 (l). Elevated temperature properties of clad 24S-T86 aluminum alloy (heat treated, cold worked, and aged) at 300° F.

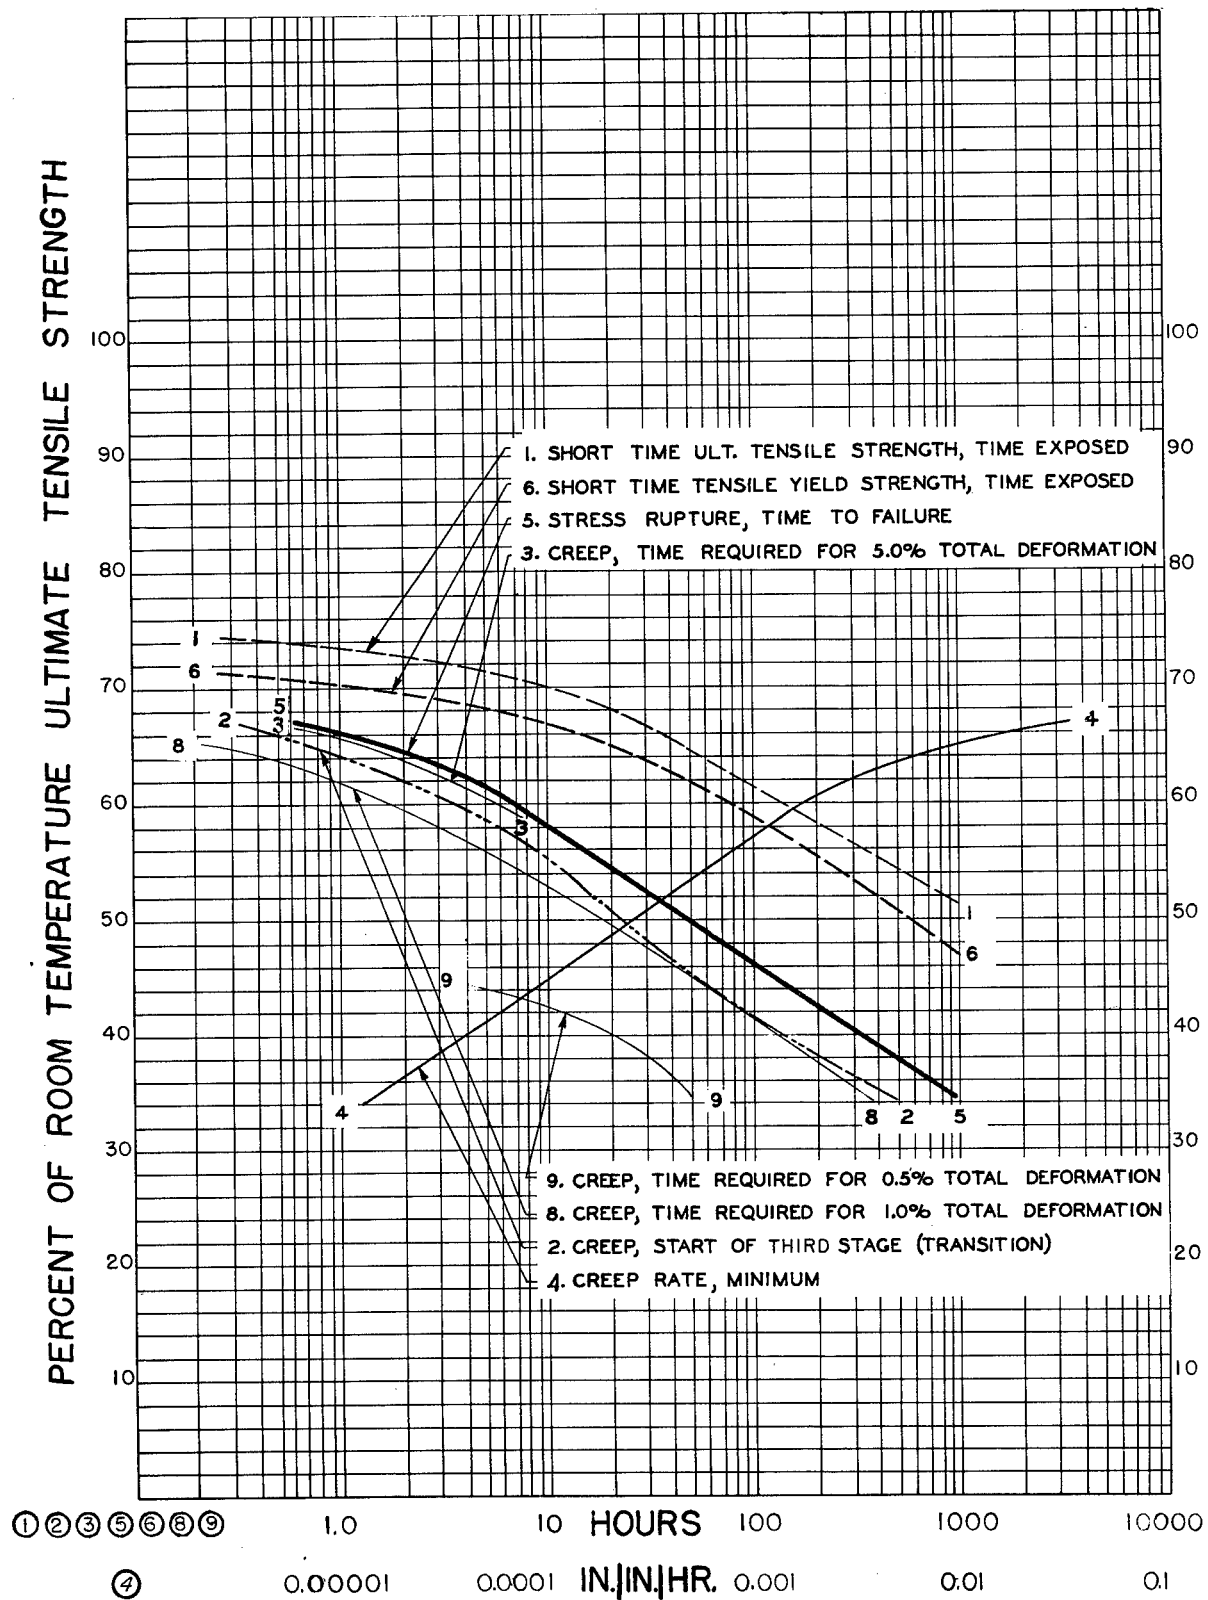

24098-P

Figure 3.1221 (m). Elevated temperature properties of clad 24S-T86 aluminum alloy (heat treated, cold worked, and aged) at 375° F.

3.1222 *Static properties.* Curves for computing the approximate reduction in tensile ultimate and tensile yield properties for various heat-treated and heat-treated and aged aluminum alloys, held unstressed at elevated temperatures up to 700° F. for various time intervals and then tested statically at temperature, are presented in figures 3.1221 (a) and (b). These data are reported in another form in figures 3.1221 (c) to (m) inclusive, for comparison with other high temperature properties. This information is based on tests which did not include any clad material, but the percentages for nonclad material are considered representative of what would be expected for the corresponding clad material. Available data on shear, bearing, and compressive properties at elevated temperatures indicates that the data in figures 3.1221 (a) and (b) may also be used to determine approximate shear, bearing, and compressive properties of aluminum alloys at elevated temperatures as follows:

(a) The percentages for tensile ultimate strength may also be applied to shear and bearing ultimate strengths.

(b) The percentages for tensile yield strength may be applied to compressive and bearing yield strengths.

The data are based on continuous heating but are considered applicable to intermittent heating when the total time at temperature is the same. The effect of high temperature on the modulus of elasticity of aluminum alloys is given in table 3.1211 (b).

3.1223 *Creep and stress-rupture properties.* Curves for computing the approximate reduction in ultimate tensile strength under long time loads, and for predicting corresponding deformations, for 24S (heat-treated), 24S (heat-treated, cold-worked, and aged), and 75S (heat-treated and aged) aluminum alloys are given in figures 3.1221 (c) to (m) inclusive, for temperatures up to 375° F. This information is based on clad sheet material only, but the percentages are considered applicable to nonclad sheet and other wrought materials of 24S heat-treated and 75S heat-treated and aged. Although no actual data are available on shear, bearing, and compression creep and stress-rupture properties at elevated temperatures, general reasoning, and known room temperature relations indicate that the data shown in figures 3.1221 (c) to (m) inclusive may be used to determine approximate, shear, bearing,

and compressive properties at elevated temperatures as follows:

(a) The percentages of the ultimate tensile strengths for rupture and transition times can be applied directly to shear and bearing ultimate strengths.

(b) The various percentages of total deformation or minimum creep rates are not directly applicable to shear and bearing but may serve as guides. The tensile values may be used for compression where deformations are not excessive.

(c) The percentages of ultimate tensile strength for determining transition times in tension may be used as guides for estimating transition times in shear and bearing.

Table 3.1224. *Cantilever beam fatigue strengths of wrought aluminum alloys at elevated temperatures*<sup>1</sup>

[Values were determined by testing 0.4-inch diameter machined specimens in Aluminum Research Laboratories fixed cantilever beam fatigue machines and represent extreme fiber stresses that such specimens will withstand in completely reversed flexure. All specimens had been stabilized by prolonged heating at testing temperature before testing. Values at 75° F. are from rotating-beam tests]

Alloy and temper	Testing temperature °F.	Fatigue strength (reversed stress), ksi at indicated number of cycles				
		100,000 cycles	1,000,000 cycles	10,000,000 cycles	100,000,000 cycles	500,000,000 cycles
14S-T6-----	75	40	32	25	20	18
	300	22.5	18	15	13	12
	400	15	12	10	8.5	8
	500	10	8.5	7	5.5	5
24S-T4-----	75	40	32	25	20	18
	300	24	20	17.5	15	14
	400	20	16	12.5	10	9
61S-T6-----	500	14	10.5	8.5	7	6
	75	31	22.5	17.5	15	13.5
	300	24	18.5	13.5	11.5	11
75S-T6-----	400	19	15	10.5	8.5	7.5
	500	7	6	5.5	4.5	4.5
	75	45	35	27	22	21
	300	18	15	13	12	12
	400	13.5	11	9.5	8.5	8.5
	500	11	9	7.5	7	7

<sup>1</sup> Data based on tests conducted by Aluminum Co. of America.

3.1224 *Fatigue properties.* Curves for computing approximate reductions in tensile ultimate strengths for 24S heat-treated and 75S heat-treated and aged aluminum alloy materials subjected to reversed loading at elevated temperatures are shown in figures 3.1221 (c) to (m) for tempera-

tures up to 375° F. This information is based on tests on cantilever beam machines in which one end of the specimen is deflected in the path of a circle subjecting the specimen to completely reversed loading. These tests include only nonclad materials but are considered applicable to clad materials. For situations involving fatigue stresses in which the mean stresses are other than zero, consideration must be given to creep and creep-rupture properties in addition to fatigue properties. Values of cantilever beam fatigue strengths of wrought aluminum alloys at elevated temperatures are given in table 3.1224. These values were determined by testing 0.4-inch diameter machined specimens in ARL fixed cantilever beam fatigue machines and represent extreme fiber stresses that such specimens will withstand in completely reversed flexure. All specimens had been stabilized by prolonged heating at testing temperature before testing. Values at 75° F. are from rotating beam tests.

**3.13 CRITERIA FOR DESIGN MECHANICAL PROPERTIES.** The test methods used to establish the design mechanical properties appearing in this chapter are discussed below, unless discussed in a note accompanying the table in which the allowances appear.

**3.131 Shear strengths.** The values of shear strengths of aluminum alloy sheet were determined by measuring the load required to punch from the sheet a 2¼-inch diameter disk, using a special punch and die. The values for other aluminum products were determined from double shear tests of cylindrical specimens in which a 1-inch length is sheared from the center of a specimen 3 inches long. In both cases, the shearing was done with hardened steel tools which have sharp smoothly finished cutting edges that are maintained in that condition.

**3.132 Tensile strengths.** The values of tensile strength of aluminum alloy materials were deter-

mined by the methods outlined in reference 1.441.

**3.133 Bearing strengths.** The values of bearing strength of aluminum alloy materials were determined by loading a steel pin inserted in a close fitting hole in material test specimens having widths at least four times the pin diameter and thicknesses not less than one-fourth the pin diameter. Tests were made for edge distances, the distance from the edge of the specimen to the center of the hole in the direction of loading, of 1.5 and two times the pin diameter. The bearing yield-strength values were obtained from bearing stress versus hole elongation curves using an offset from the initial straight line portion of the curves of 2 percent of the pin diameter. See references 3.133.

**3.14 RATE OF STRESSING EFFECTS.** A knowledge of the effect of the rate of loading on the load-deformation characteristics of aluminum alloys is important since the aircraft structure in which the material is used is subjected to various loading rates depending on aircraft speed, gust sizes and velocities, maneuver conditions and alighting conditions. Sufficient information is available for the higher strength aluminum alloys to establish that the effect of rate of loading on their load-deformation characteristics at room temperature is insignificant. However, no data are available from this investigation for the lower strength material such as 2S and 3S for any of the alloys at low and elevated temperatures. However, there is some evidence from impact tests as described in NACA TN 2082 and from other sources that at low temperatures rate of stressing is no more critical than at room temperature.

## 3.2 Columns

**3.21 PRIMARY FAILURE.** The general formulas for primary instability are given in section 1.38. For convenience, these formulas are repeated in table 3.21 in simplified form applicable to round

Table 3.21. Column formulas for Aluminum Alloy Tubing and/or Shapes


Material	$F_{co}$	Short columns	Critical $L'/\rho$	Long columns	Local failure
24S-T3 and T4, 14S-T4, and 61S-T6.	$F_{cv} \left[ 1 + \frac{F_{cv}}{200,000} \right]$	Equation 1.385	$1.732\pi\sqrt{E/F_{co}}$	Equation 1.381	(*)
75S-T6	$1.075 F_{cv}$	Equation 1.383	$1.414\pi\sqrt{E/F_{co}}$	Equation 1.381	(*)

\*Must be determined by test unless conservatively assumed.


$\frac{L'}{\rho} = \frac{L}{\sqrt{c\rho}}$ ;  $L'/\rho$  shall not exceed 150 without specific authority from the procuring or certifying agency.

Critical  $L'/\rho$  is that above which the columns are "long" and below which they are "short."

Equation 1.381 (a) may be used in the short column range if  $E'$  is replaced by  $E_c$  obtained from the compressive stress-strain curve for the material.

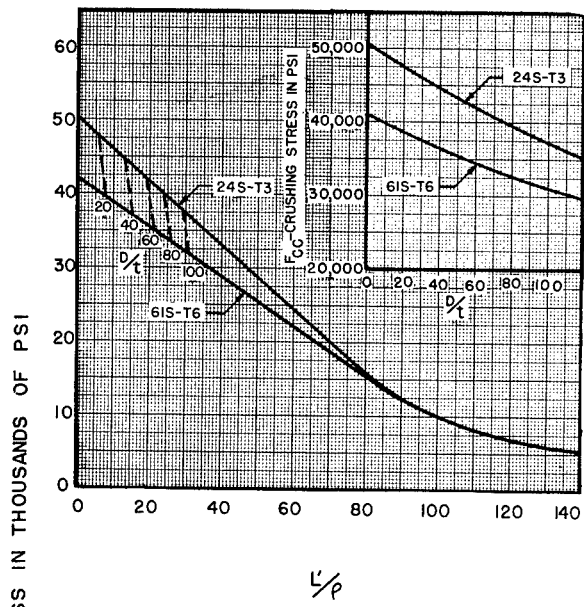

(A) ROUND 24S AND 61S TUBING

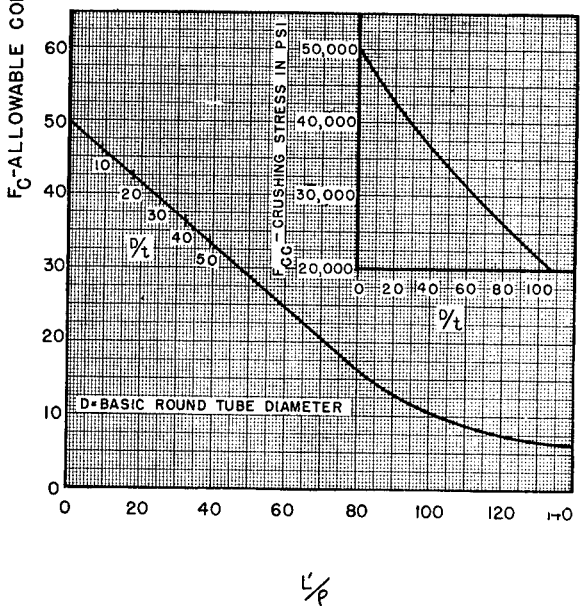

(B) STREAMLINE 24S-T3 TUBING

Figure 3.23. Allowable column and crushing stresses 24S and 61S aluminum alloy tubing.

aluminum alloy tubes. These formulas can also be used for columns having cross sections other than those of round tubes when local instability is not critical.

3.22 LOCAL FAILURE. Table 3.21 also contains notes and references concerning the local instability of round tubes.

3.23 COLUMN STRESS CURVES. Curves of the allowable column stresses for round and streamline tubing are given in figure 3.23. The allowable stress is plotted against the effective slenderness ratio defined by the formula:

$$\frac{L'}{\rho} = \frac{L}{\sqrt{c\rho}} \dots\dots\dots (3.231)$$

3.3 Beams

3.31 GENERAL. See equation 1.323; section 1.525; and reference 1.71 for general information on stress analysis of beams.

3.32 SIMPLE BEAMS. Beams of solid, tubular, or similar cross sections can be assumed to fail

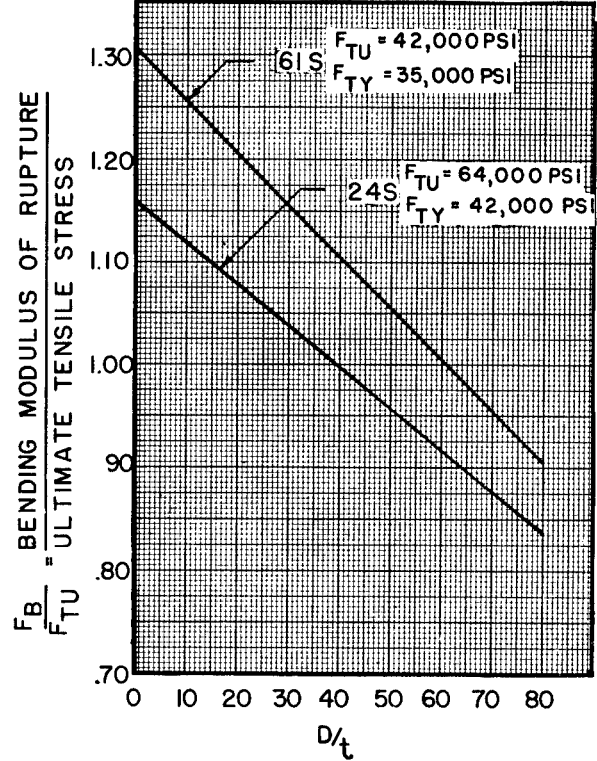


Figure 3.321. Bending modulus of rupture aluminum alloy round tubing restrained against local buckling at loading points.

through exceeding an allowable modulus of rupture in bending ( $F_b$ ). For solid sections it can usually be safely assumed  $F_b$  equals the ultimate tensile stress.

3.321 Round tubes. For round tubes the value of  $F_b$  will depend on the  $D/t$  ratio as well as the ultimate tensile stress. The bending modulus of rupture of 24S and 61S round tubes is given in figure 3.321. It should be noted that these values apply only when the tubes are restrained against local buckling at the loading points.

3.322 *Unconventional cross sections.* Sections other than solid or tubular should be tested to determine the allowable bending stress.

3.33 **BUILT-UP BEAMS.** Built-up beams will usually fail due to local failures of the component parts. In aluminum alloy construction the strength of fittings and joints is an important feature.

3.34 **THIN-WEB BEAMS.** The allowable stresses for thin-web beams will depend on the nature of the failure and are determined from the allowable stresses of the web in tension and of the flanges or stiffeners in compression.

### 3.4 Torsion

3.41 **GENERAL.** The torsional failure of aluminum-alloy tubes may be due to plastic failure of the metal, elastic instability of the walls, or to an intermediate condition. Pure shear failure will not usually occur within the range of wall thicknesses commonly used for aircraft tubing.

3.42 **ALLOWABLE TORSIONAL SHEAR STRESSES.** In the range of low values of  $D/t$  no theoretical formula is directly applicable. The results of tests have been used to determine the empirical curves of figure 3.42.

### 3.5 Combined loadings

3.51 **ROUND TUBES IN BENDING AND COMPRESSION.** The general theory of failure under combined loadings is given in section 1.535. In the case of combined bending and compression it is necessary to consider the effects of secondary bending, that is, bending produced by the axial load acting in conjunction with the lateral deflection of the column. In general, equation 1.5353, can be used in the following forms for safe values:

$$(f'_b/F_b) + (f_c/F_{cy}) = 1.0 \dots \dots (3.511)$$

$$M. S. = \frac{1}{(R'_b + R_c)} - 1 \dots \dots (3.511a)$$

where

$f'_b$  = maximum bending stress including effects of secondary bending.

$F_b$  = Bending modulus of rupture.

$f_c$  = Axial compressive stress.

$F_{cy}$  = Compressive yield stress.

In no case shall the axial compressive stress,  $f_c$ , exceed the allowable stress,  $F_c$ , for a simple column.

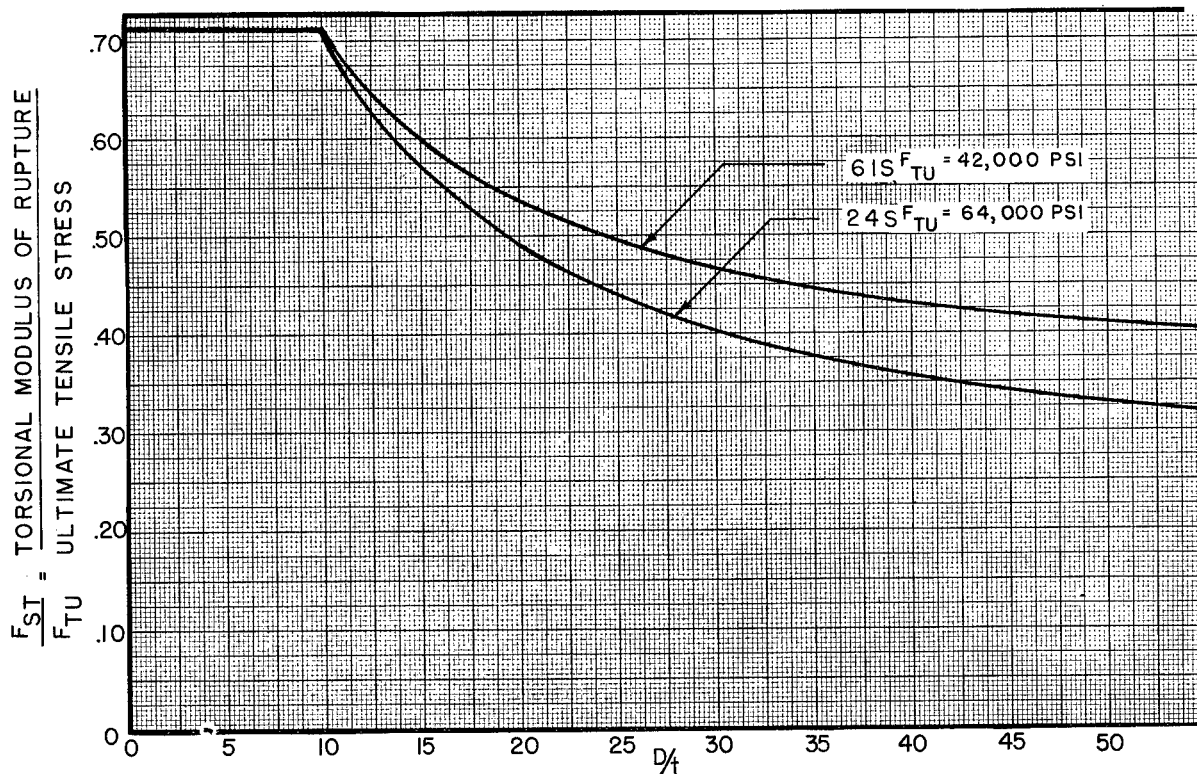


Figure 3.42. Torsional modulus of rupture—aluminum alloy round tubing.

3.52 TUBES IN BENDING AND TORSION. Equation 1.5353, can be used in the following forms for safe values:

$$(f_b/F_b)^2 + (f_s/F_{st})^2 = 1.0 \text{-----} (3.521)$$

Round tubes:

$$R_b^2 + R_s^2 = 1.0 \text{-----} (3.521a)$$

$$\text{M. S.} = \frac{1}{\sqrt{(R_b)^2 + (R_s)^2}} - 1 \text{----} (3.521b)$$

Streamline tubes:

$$R_b + R_s = 1.0 \text{-----} (3.522)$$

$$\text{M. S.} = \frac{1}{R_b + R_s} - 1 \text{-----} (3.522a)$$

$f_s$  = Shear stress.

$F_{st}$  = Torsional modulus of rupture.

Higher values can be used if substantiated by adequate test data.

3.53 TUBES IN BENDING, COMPRESSION AND TORSION. The bending stresses should include the effects of secondary bending due to compression. The following empirical equation will serve as a working basis, pending a more thorough investigation of the subject:

$$[f_b'/F_b]^2 + [f_s/F_{st}]^2 = [1 - f_c/F_{cv}]^2 \text{----} (3.531)$$

$$\text{M. S.} = \frac{1}{R_c + \sqrt{(R_b')^2 + (R_s)^2}} - 1 \text{----} (3.531a)$$

In no case shall the axial compressive stress,  $f_c$ , exceed the allowable stress,  $F_c$ , for a simple column.

### 3.6 Joints, fittings, and parts

#### 3.61 JOINTS

3.611 *Riveted and bolted joints.* In order to determine the strength of such joints it is necessary to know the strength of the individual rivets or

bolts. In most cases, such joint failures occur by shearing the connecting element, or by bearing and/or tearing the sheet or plate.

3.6111 *Protruding head rivets and bolts.* The load per rivet or bolt at which the shear or bearing type of failure occurs is separately calculated and the lower of the two governs the design. The basic shear strengths for protruding head aluminum alloy rivets are given in table 3.6111 (a). Basic shear strengths for protruding head steel bolts, and pins are given in tables 2.6111. In computing aluminum rivet design shear strengths, the correction factors given in table 3.6111 (a) should be used to compensate for the reductions in rivet shear strength resulting from high bearing stresses on the rivet at  $D/t$  ratios in excess of 3.0 for single shear joints, and 1.5 for double shear joints (reference No. 3.6111). The design bearing stresses for aluminum alloys given in tables 3.111 are applicable to riveted or bolted joints wherein cylindrical holes are used and where  $D/t < 5.5$ ; where  $D/t > 5.5$ , tests to substantiate yield and ultimate bearing strengths must be made. Yield strengths of rivets or bolts may be computed in a manner similar to ultimate strengths except that the factors of table 3.6111 (a) need not be applied. The bearing yield stresses correspond to a permanent set in the hole (in a single sheet) equal to two percent of the hole diameter. These bearing stresses are applicable only for the design of rigid joints where there is no possibility of relative movement of the parts joined without deformation of such parts. For other types of joints the design bearing stresses are to be reduced by dividing by the factors of safety specified in table 2.61122 (a). For convenience, "unit" sheet bearing strengths on rivets based on a stress of 100 *ksi* and nominal hole diameters are given in table 3.6111 (d). Factors representing the ratio of actual sheet bearing strengths to 100 *ksi* are given in table 3.6111 (b). Table 2.61121 contains "unit" sheet bearing strengths on bolts.



Table 3.6111 (a). Shear Strengths of Protruding and Flush Head Aluminum Alloy Rivets (Pounds)

Diameter of rivet.....	$\frac{1}{16}$	$\frac{3}{32}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{5}{16}$	$\frac{3}{8}$
56S— $F_{su}=27$ ksi.....	95	195	350	536	774	1,400	2,210	3,160
A17S-T3— $F_{su}=30$ ksi.....	106	217	388	596	862	1,550	2,460	3,510
17S-T31— $F_{su}=34$ ksi.....	120	247	442	675	977	1,760	2,790	3,970
17S-T3— $F_{su}=38$ ksi.....	135	275	494	755	1,090	1,970	3,110	4,450
24S-T31— $F_{su}=41$ ksi.....	145	296	531	815	1,180	2,120	3,360	4,800

## SINGLE SHEAR RIVET STRENGTH FACTORS

Sheet thickness:								
0.014.....								
0.016.....	0.964							
0.018.....	.984							
0.020.....	.996							
0.025.....	1.000	0.972						
0.032.....		1.000	0.964					
0.036.....			.980					
0.040.....			.996	0.964				
0.045.....			1.000	.980				
0.051.....				.996	0.972			
0.064.....				1.000	1.000	0.964		
0.072.....						.980	0.964	
0.081.....						.996	.974	
0.091.....						1.000	.984	
0.102.....							.996	0.972
0.128.....							1.000	1.000
0.156.....								
0.188.....								
0.250.....								

## DOUBLE SHEAR RIVET STRENGTH FACTORS

Sheet thickness:								
0.014.....								
0.016.....	0.688							
0.018.....	.753							
0.020.....	.792							
0.025.....	.870	0.714						
0.032.....	.935	.818	0.688					
0.036.....	.974	.857	.740					
0.040.....	.987	.896	.792	0.688				
0.045.....	1.000	.922	.831	.740				
0.051.....		.961	.870	.792	0.714			
0.064.....		1.000	.935	.883	.818	0.688		
0.072.....			.974	.919	.857	.740		
0.081.....			1.000	.948	.896	.792	0.688	
0.091.....				.974	.922	.831	.753	
0.102.....				1.000	.961	.870	.792	0.714
0.128.....					1.000	.935	.883	.818
0.156.....						.987	.935	.883
0.188.....						1.000	.974	.935
0.250.....							1.000	1.000

## NOTE

Values of shear strength should be multiplied by the factors given herein whenever the  $D/t$  ratio is large enough to require such a correction.

Shear values are based on areas corresponding to the nominal hole diameters specified in table 3.6111 (c) note e.

Shear stresses in table 3.6111 (c) corresponding to 90 percent probability data are used wherever available.

Sheet thickness is that of the thinnest sheet in single shear joints and of the middle sheet in double shear joints.

Table 3.6111 (b). Aluminum Alloy Sheet and Plate—Bearing Factors <sup>1</sup>[ $K$ =ratio of actual bearing strength to 100 ksi]

Material	Thickness	A values (minimum guaranteed properties)				B values (probability values)			
		$K$ ultimate		$K$ yield		$K$ ultimate		$K$ yield	
		$e/D=2.0$	$e/D=1.5$	$e/D=2.0$	$e/D=1.5$	$e/D=2.0$	$e/D=1.5$	$e/D=2.0$	$e/D=1.5$
24S-T4 (heat-treated by user)	< 0.250	1.18	0.93	0.64	0.56				
24S-T42 (heat-treated by user)	0.250-0.500	1.22	.96	.61	.53				
	.501-1.000	1.18	.93	.61	.53				
	1.001-2.000	1.14	.90	.61	.53				
24S-T3	2.001-3.000	1.06	.84	.61	.53				
	< .250	1.24	.98	.79	.69	1.29	1.02	0.82	0.71
24S-T4	.250- .500	1.24	.98	.74	.64	1.27	1.01	.78	.69
	.501-1.000	1.20	.95	.70	.62	1.29	1.02	.77	.67
24S-T36	1.001-2.000	1.16	.92	.68	.60	1.22	.96	.75	.66
	< .500	1.33	1.05	.96	.84	1.37	1.08	1.00	.88
24S-T4 (coiled)	< .250	1.18	.93	.64	.56	1.26	.99	.66	.57
Clad 24S-T4 (heat-treated by user)	< .064	1.10	.87	.59	.52				
	.064- .249	1.16	.92	.61	.53				
	.250- .499	1.18	.93	.61	.53				
Clad 24S-T4 (heat-treated by user)	.500-1.000	1.14	.90	.58	.50				
	1.001-2.000	1.10	.87	.58	.50				
	2.001-3.000	1.03	.81	.58	.50				
Clad 24S-T3	.010- .063	1.14	.90	.73	.64	1.18	.93	.76	.67
	.064- .249	1.20	.95	.74	.64	1.24	.98	.78	.69
	.250- .499	1.20	.95	.74	.64	1.24	.98	.78	.69
Clad 24S-T4	.500-1.000	1.16	.92	.67	.59	1.24	.98	.74	.64
	1.001-2.000	1.12	.89	.64	.56	1.18	.93	.70	.62
	.019- .063	1.20	.95	.88	.77	1.25	.99	.93	.81
Clad 24S-T36	.064- .500	1.27	1.01	.93	.81	1.31	1.04	.96	.84
	.012- .063	1.10	.87	.59	.52	1.16	.92	.61	.53
Clad 24S-T4 (coiled)	.064	1.16	.92	.61	.53	1.20	.95	.64	.56
	< .064	1.14	.90	.75	.66				
Clad 24S-T6	> .064	1.18	.93	.78	.69				
	< .064	1.22	.96	.90	.78				
Clad 24S-T81	> .064	1.27	1.00	.94	.83				
	< .064	1.27	1.00	1.01	.88				
Clad 24S-T84	> .064	1.33	1.05	1.06	.92				
	< .064	1.33	1.05	1.04	.91				
Clad 24S-T86	> .064	1.35	1.06	1.09	.95				
	.016- .039	1.44	1.14	1.06	.92	1.48	1.17	1.10	.97
	.040- .249	1.46	1.16	1.07	.94	1.50	1.19	1.12	.98
75S-T6 (aged)	.250- .500	1.46	1.16	1.07	.94	1.50	1.19	1.10	.97
	.501-1.000	1.50	1.19	1.10	.97	1.56	1.23	1.15	1.01
	1.001-2.000	1.50	1.19	1.10	.97				
Clad 75S-T6 (aged)	.016- .039	1.33	1.05	.98	.85	1.39	1.10	1.02	.90
	.040- .249	1.37	1.08	1.01	.88	1.41	1.11	1.04	.91
	.250- .499	1.37	1.08	1.01	.88	1.41	1.11	1.04	.91
Hardclad R301-T3 and Alclad 14S-T3	.500-1.000	1.41	1.11	1.02	.90	1.44	1.14	1.07	.94
	1.001-2.000	1.41	1.11	1.02	.90				
Hardclad R301-T6 and Alclad 14S-T6	.020- .039	1.06	.84	.64	.56				
	.040- .250	1.08	.85	.69	.60				
52S-H32 (¼H)	.020- .039	1.20	.94	.90	.78				
52S-H34 (½H)	.040- .250	1.22	.96	.91	.80				
52S-H36 (¾H)		.65	.50	.34	.29				
52S-H38(II)		.71	.54	.38	.34				
61S-T4		.78	.59	.46	.41				
61S-T6		.82	.62	.53	.46				
		.63	.48	.26	.22				
		.88	.67	.56	.49				

<sup>1</sup> For  $e/D$  values between 1.5 and 2.0 bearing factors may be obtained by linear interpolation ( $e$ =edge distance,  $D$ =hole diameter).

Table 3.6111 (c). Design Mechanical Properties for Aluminum Alloy Rivets (Kips Per Square Inch)

Type.....	Protruding head rivets <sup>a</sup>								
	A17S		17S		24S		56S		
Alloy.....	MIL-R-5674								
Specification.....	(T3)		(T31) <sup>b</sup>		(T3) <sup>c</sup>		(T31)		(H-321)
Condition.....	A	B	A	B	A	B	A	B	A
Basis <sup>d</sup> .....									
$F_{su}$ <sup>e</sup> .....	28	30	33	34	35	38	37	41	27

<sup>a</sup> The driven head diameter shall be at least 1.3 times the nominal shank diameter of the rivet.

<sup>b</sup> The 17S-T31 designation refers to rivets that have been heat treated and then maintained in the heat treated condition until driving.

<sup>c</sup> The 17S-T3 designation refers to 17S rivets which are fully aged at room temperature for at least 4 days after quenching, and then driven. (The higher strength properties of the 17S-T3 rivets result from the cold-working effects obtained when the rivets are driven in the aged condition).

<sup>d</sup> A is the mechanical property column based upon the minimum guaranteed tensile properties; B is the mechanical property column based upon probability data. (See par. 3.111.)

<sup>e</sup> Shear and bearing strength values for driven rivets may be based on areas corresponding to the nominal hole diameter provided that the nominal hole diameter is not larger than the values listed below. If the nominal hole diameter is larger than the listed values the listed value shall be used.

Standard rivet hole drill sizes and nominal hole diameters

Rivet size.....	$\frac{1}{16}$	$\frac{3}{32}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{5}{16}$	$\frac{3}{8}$
Drill No.....	51	41	30	21	11	F	P	W
Nominal hole diameter.....	0.067	0.096	0.1285	0.159	0.191	0.257	0.323	0.386

Table 3.6111 (d). Unit Bearing Strength of Sheet on Rivets  $F_{br}=100,000$  psi (Pounds)

Diameter of rivet	$\frac{1}{16}$	$\frac{3}{32}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{5}{16}$	$\frac{3}{8}$
Sheet thickness:								
0.014.....	44							
0.016.....	107							
0.018.....	121	173						
0.020.....	134	192						
0.025.....	168	240	321					
0.032.....	214	307	411	509				
0.036.....	241	346	463	572	688			
0.040.....	268	384	514	636	764			
0.045.....	302	432	578	716	860			
0.051.....	342	490	655	811	974	1,310		
0.064.....	429	614	822	1,020	1,220	1,640	2,070	
0.072.....	482	691	925	1,140	1,370	1,850	2,330	2,780
0.081.....	543	778	1,040	1,290	1,550	2,080	2,620	3,130
0.091.....	610	874	1,170	1,450	1,740	2,340	2,940	3,510
0.102.....	683	979	1,310	1,620	1,910	2,620	3,290	3,940
0.128.....	858	1,230	1,640	2,030	2,410	3,290	4,130	4,940
0.156.....	1,050	1,500	2,010	2,480	2,980	4,010	5,040	6,030
0.188.....	1,250	1,800	2,410	2,980	3,580	4,820	6,060	7,240
0.250.....	1,670	2,400	3,210	3,970	4,770	6,420	8,070	

Bearing values are based on areas corresponding to the nominal hole diameters specified in table 3.6111 (c).

3.6112 *Flush rivets.* Tables 3.6112 contain ultimate and yield allowable single-shear strength values for both machine countersunk and dimpled flush riveted joints employing solid rivets with a head angle of 100°. These strength values are applicable when the edge distance is equal to or

greater than two times the nominal rivet diameter. Other strength values and edge distances may be used if substantiated by tests.

The allowable ultimate loads were established from test data using the average failing load divided by a factor of 1.15. The yield loads were

established from test data wherein the yield load was defined as the average test load at which the following permanent set across the joint is developed.

(a) 0.005 inch up to and including  $\frac{3}{16}$  inch diameter rivets.

(b) 2.5 percent of the rivet diameter for rivet sizes larger than  $\frac{3}{16}$  inch diameter.

Test data from which the yield and ultimate strengths listed were derived are to be found in reference 3.6112.

Table 3.6112 (a). Ultimate Strength of Solid 100° Machine Countersunk Rivets (Pounds)

Rivet material.....	A17S-T3				17S-T3			24S-T31		
	24S-T3, 24S-T6, 24S-T81, 24S-T86, and 75S-T6									
Clad sheet material.....										
$t^a$ \ D	$\frac{3}{32}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{3}{16}$	$\frac{1}{4}$	
0.020.....	132									
0.025.....	156									
0.032.....	178	272								
0.040.....	193	309	*418		*476					
0.051.....	206	340	*479	*628	*580	*726		758		
0.064.....	216	363	523	705	*657	*859		886	*1, 290	
0.072.....		373	542	739	690	*917	*1, 338	942	*1, 424	
0.081.....			560	769	720	*969	*1, 452	992	*1, 543	
0.091.....			575	795	746	1, 015	*1, 552	1, 035	*1, 647	
0.102.....				818		1, 054	*1, 640	1, 073	*1, 738	
0.125.....				853		1, 090	1, 773	1, 131	1, 877	
0.156.....							1, 891		2, 000	
0.188.....							1, 970		2, 084	
0.250.....										

<sup>a</sup> Sheet gage is that of the upper sheet.

In cases where the lower sheet is thinner than the upper the shear-bearing allowable for the lower sheet-rivet combination should be computed.

The values in this table are based on "good" manufacturing practice, and

any deviation from this will produce significantly reduced values.

Yield values of the sheet-rivet combinations marked thus (\*) are less than  $\frac{2}{3}$  of the indicated ultimate values.

Table 3.6112 (b). Yield Strength of Solid 100° Machine Countersunk Rivets (Pounds)

Rivet material.....	A17S-T3				17S-T3			24S-T31		
	24S-T3, 24S-T6, 24S-T81, 24S-T86, and 75S-T6									
Clad sheet material.....										
$t^a$ \ D	$\frac{3}{32}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{3}{16}$	$\frac{1}{4}$	
0.020.....	91									
0.025.....	113									
0.032.....	132	198								
0.040.....	153	231	265		270					
0.051.....	188	261	321	389	345	419		538		
0.064.....	213	321	402	471	401	515		614	811	
0.072.....		348	453	538	481	557	706	669	902	
0.081.....			498	616	562	623	788	761	982	
0.091.....			537	685	633	746	861	842	1, 053	
0.102.....				745		854	1, 017	913	1, 115	
0.125.....				836		1, 018	1, 313	1, 021	1, 357	
0.156.....							1, 574		1, 694	
0.188.....							1, 753		1, 925	
0.250.....										

<sup>a</sup> Sheet gage is that of the upper sheet.

In cases where the lower sheet is thinner than the upper the shear-bearing allowable for the lower sheet-rivet combination should be computed.

The values in this table are based on "good" manufacturing practice, and any deviation from this will produce significantly reduced values.

Table 3.6112 (c). Ultimate Strength of Solid 100° Dimpled Rivets (Pounds)

Rivet material.....	A17S-T3								17S-T3						24S-T31				
	24S-T3, 24S-T6, and 24S-T81		24S-T86	24S-T3		24S-T6, 24S-T81, 24S-T86, 75S-T6		24S-T3, 24S-T6, and 24S-T81		24S-T86 and 75S-T6		24S-T3	24S-T6, 24S-T81, 24S-T86, and 75S-T6	24S-T3		24S-T6, 24S-T81, 24S-T86, and 75S-T6			
$t^a$ \ D	$\frac{3}{32}$	$\frac{1}{8}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{1}{4}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{3}{16}$	$\frac{1}{4}$	
0.016.....	177																		
0.020.....	209	299	302																
0.025.....	235	360	383	474			462		419		530								
0.032.....	257	413	454	568	722	599	725		600	681	672	822			744		786		
0.040.....	273	451	505	635	839	695	891		728	905	775	1,000	845	1,108	941	879	982	1,300	
0.051.....		484	548	693	940	778	1,036		840	1,097	864	1,153	1,332	1,508	1,110	1,359	1,152	1,705	
0.064.....				736	1,012	840	1,142		922	1,240	930	1,267	1,695	1,803	1,236	1,727	1,277	2,010	
0.072.....				755	1,045	867	1,190		958	1,301	957	1,315	1,853	1,930	1,291	1,883	1,332	2,150	
0.081.....					1,074		1,230			1,357		1,358	1,995	2,044	1,340	2,025	1,380	2,260	
0.091.....					1,098		1,267			1,405		1,398	2,115	2,145	1,382	2,150	1,424	2,365	
0.102.....													2,220	2,232		2,255		2,455	

<sup>a</sup> The above allowables apply to double dimpled sheets and to the upper sheet dimpled into a machine countersunk lower sheet. Sheet gage is that of the thinnest sheet for double dimpled joints and of the upper dimple sheet for dimpled-machine countersunk joints. The thickness of the machine countersunk sheet must be at least 1 tabulated gage thicker than the upper sheet.

In no case shall allowables be obtained by extrapolation for skin gages other than those shown.

The values in this table are based on "good" manufacturing practice and any deviation from this will produce significantly reduced values.

Table 3.6112 (d). Yield Strength of Solid 100° Dimpled Rivets (Pounds)

Rivet material.....	A17S-T3								17S-T3						24S-T31				
	24S-T3, 24S-T6, and 24S-T81		24S-T3, 24S-T6, 24S-T81, and 24S-T86	24S-T3, 24S-T6, and 24S-T81		24S-T86, and 75S-T6		24S-T3, 24S-T6, and 24S-T81		24S-T86 and 75S-T6		24S-T3	24S-T6 and 24S-T81	24S-T86 and 75S-T6					
$t^a$ \ D	$\frac{3}{32}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{3}{16}$	$\frac{1}{4}$	
0.016.....	154																		
0.020.....	184	257																	
0.025.....	209	315	324		410		336		450										
0.032.....	231	367	430	512	525	640	483	546		581	705		582		649		786		
0.040.....	246	404	506	644	606	782	589	730	845	675	867	978	666	879	816	962	982	978	
0.051.....		436	571	757	677	905	681	888	1,187	756	1,007	1,508	738	1,308	961	1,308	1,152	1,543	
0.064.....			619	841	729	995	748	1,006	1,415	816	1,111	1,803	925	1,564	1,068	1,564	1,277	1,958	
0.072.....			641	878	752	1,034	778	1,056	1,656	842	1,156	1,930	1,045	1,711	1,115	1,711	1,332	2,140	
0.081.....				910		1,070		1,102	1,870		1,196	2,044	1,152	1,928	1,177	1,928	1,380	2,260	
0.091.....				939		1,100		1,142	2,057		1,231	2,145	1,246	2,121	1,324	2,121	1,424	2,365	
0.102.....									2,220			2,232		2,255		2,268		2,455	

<sup>a</sup> The above allowables apply to double dimpled sheets and to the upper sheet dimpled into a machine countersunk lower sheet. Sheet gage is that of the thinnest sheet for double dimpled joints and of the upper dimpled sheet for dimpled-machine countersunk joints. The thickness of the machine countersunk sheet must be at least 1 tabulated gage thicker than the upper sheet.

In no case shall allowables be obtained by extrapolation for skin gages other than those shown.

The values in this table are based on "good" manufacturing practice and any deviation from this will produce significantly reduced values.

3.6113 *Blind rivets.* Tables 3.6113 contain ultimate and yield allowable single shear strengths for protruding head and flush head blind rivets in aluminum alloy sheet. These strengths are applicable only when the grip lengths and rivet hole tolerances are as recommended by the respective rivet manufacturers. These strengths may be substantially reduced if oversize holes or improper grip lengths are used.

The strength values were established from test data obtained from tests of specimens having edge distances  $e/D$  equal to or greater than 2.0. Where  $e/D$  values less than 2.0 are used tests to substantiate yield and ultimate bearing strengths must be made. Ultimate strength values of protruding and flush blind rivets were obtained from the average failing load of test specimens divided by 1.15. Yield strength values were obtained from average yield load test data wherein the yield load is defined as the load at which the following permanent set across the joint is developed.

(a) 0.005 inches up to and including  $\frac{3}{16}$ -inch-diameter rivets.

(b) 2.5 percent of the rivet diameter for rivet sizes larger than  $\frac{3}{16}$ -inch-diameter.

Blind rivets should not be used in applications where appreciable tensile loads on the rivets will exist. Reference should be made to the requirements of the applicable procuring or certifying agency relative to the use of blind rivets.

Table 3.6113 (a). Rivet Shear Strengths for Blind Rivets (Protruding and Flush Heads) (Pounds)

STANDARD-SIZE RIVETS <sup>1</sup>				
Rivet type	Rivet diameter			
	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{5}{16}$	$\frac{3}{8}$
Cherry (CR156, CR157).....	395	605	875	1, 580
Cherry (CR162, CR163).....	415	635	917	1, 660
Huck (P, 100V).....	445	684	986	.....

OVERSIZE RIVETS <sup>2</sup>				
Cherry (CR178, CR179).....	472	788	1, 065	.....
DuPont (DR, DR-100).....	435	725	1, 015	.....

<sup>1</sup> Shear strengths computed using nominal hole size and probability shear values for rivet and pin materials as shown in table 3.6111 (c).

<sup>2</sup> Shear strengths computed using rivet diameter before driving and probability shear values for rivet and pin materials as shown in table 3.6111 (c).

Table 3.6113 (b). Ultimate and Yield Strengths for Protruding Head Blind Rivets (Pounds)

ULTIMATE STRENGTH

Rivet type	Standard-size rivets									Oversize rivets						
	Cherry (CR 157)			Cherry (CR 163)				Huck (P)		Cherry (CR 179)			DuPont (DR)			
Sheet material	24S-T3, Clad 24S-T3, Clad 24S-T6, Clad 24S-T81, Clad 24S-T84, Clad 24S-T86, and Clad 75S-T6			24S-T3, Clad 24S-T3, Clad 24S-T6, Clad 24S-T81, Clad 24S-T84, Clad 24S-T86 and Clad 75S-T6				Clad 24S-T3		24S-T3, Clad 24S-T3, Clad 24S-T6, Clad 24S-T81, Clad 24S-T84, Clad 24S-T86, and Clad 75S-T6			24S-T3			
$t^a$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$
0.025	225	278		232	298			253	280	326	260	300	310	270		
0.032	260	334	425	282	420	520		344	455	492	305	420	460	355	435	460
0.040	310	400	495	337	490	594	694	390	505	647	355	520	610	420	555	665
0.051	370	480	598	372	555	690	1,092	402	604	856	430	605	770	435	660	840
0.064	395	572	723	414	635	813	1,290	422	665	908	472	680	900	435	725	960
0.072	395	605	787	415	635	880	1,380		678	957	472	725	955	435	725	1,000
0.081	395	605	851			917	1,485			967		765	1,000			
0.091		605	875			917	1,550					788	1,040			
0.102		605	875				1,660						1,065			
0.125			875				1,660						1,065			

YIELD STRENGTHS

0.025	225	278		232	298			233	280	326	240	275	285	210		
0.032	260	334	425	282	392	520		268	364	472	280	385	415	275	335	360
0.040	310	400	495	325	460	570	694	300	402	530	330	470	550	325	430	510
0.051	362	480	598	372	545	660	930	316	499	680	395	555	705	355	510	660
0.064	395	561	723	410	635	765	1,130	401	540	688	450	625	835	360	550	750
0.072	395	600	787	415	635	820	1,260		546	820	450	660	875		575	780
0.081	395	605	851			865	1,380			820		700	920			
0.091		605	875			870	1,460					740	960			
0.102		605	875				1,530						990			
0.125			875				1,600						990			

Other sheet-rivet combinations may be used subject to specific approval of the procuring or certifying agency.

<sup>a</sup> Sheet gage is that of the thinnest sheet.

Table 3.6113 (c). Ultimate and Yield Strengths for 100° Double Dimpled Blind Rivets (Pounds)

ULTIMATE STRENGTHS

Rivet type	Standard-size rivets									Oversize rivets						
	Cherry (CR 156) (2)			Cherry (CR 162) (2)				Huck (100V)		Cherry (CR 178) (2)			DuPont (DR-100)			
Sheet material	24S-T3, Clad 24S-T3, Clad 24S-T6, Clad 24S-T81, Clad 24S-T84, Clad 24S-T86, and Clad 75S-T6			24S-T3, Clad 24S-T3, Clad 24S-T6, Clad 24S-T81, Clad 24S-T84, Clad 24S-T86, and Clad 75S-T6				Clad 24S-T3		24S-T3, Clad 24S-T3, Clad 24S-T6, Clad 24S-T81, Clad 24S-T84, Clad 24S-T86, and Clad 75S-T6			24S-T3			
$t_s$ $D$	1/8	5/32	3/16	1/8	5/32	3/16	1/4	1/8	5/32	3/16	1/8	5/32	3/16	1/8	5/32	3/16
0.020	170			*159										304	387	
0.025	185	290		252	368			255	375	*464	235	335	455	366	503	
0.032	205	315	460	252	368	490		266	400	493	285	400	520	519	678	830
0.040	225	348	485	269	395	528	*832	340	513	694	330	465	610	570	776	1,021
0.051	255	390	520	298	440	578	1,005	428	545	824	380	550	725	611	969	1,177
0.064		445	565		482	636	1,125		684	900	380	610	785		988	1,290
0.072			590			655	1,190			981		610	785			1,330
0.081			620			683	1,290			986						1,395
0.091							1,410									
0.102							1,535									

YIELD STRENGTHS

0.020	170			99										285	310	
0.025	185	290		242	290			255	304	289	230	268	320	362	400	
0.032	205	315	460	252	368	440		266	369	404	272	386	450	495	487	695
0.040	225	348	485	269	395	440	550	294	410	480	310	465	575	525	595	790
0.051	255	390	520	298	432	517	700	366	473	554	358	550	725	611	810	825
0.064		445	563		482	636	890		683	645	358	610	785		835	870
0.072			578			655	950			775		610	785			905
0.081			588			683	1,030			809						1,025
0.091							1,190									
0.102							1,350									

\* Sheet gage is that of the thinnest sheet.

In the case of Cherry Rivet Co. rivets only, the above allowables also apply to dimpled-machine countersunk joints. In this case the allowable is determined by the gage of the upper dimpled sheet. The gage of the lower machine countersunk sheet must be at least 1½ times the height of the preformed rivet head for standard size rivets and twice the height of the preformed rivet head for oversize rivets. Allowables for the DuPont Co.

and Huck Rivet Co. rivets for dimpled-machine countersunk installations are not available.

In no case shall allowables be obtained by extrapolation for skin gages other than those shown.

Yield values of the sheet-rivet combinations marked thus (\*) are less than ¾ of the indicated ultimate values.

Other sheet-rivet combinations may be used subject to specific approval of the procuring or certifying agency.



Table 3.6113 (d). Ultimate and Yield Strengths for 100° Machine Countersunk Blind Rivets (Pounds)

## ULTIMATE STRENGTHS

Rivet type.....	Standard-size rivets									Oversize rivets						
	Cherry (CR 156)			Cherry (CR 162)				Huck (100V)		Cherry (CR 178)			DuPont (DR-100)			
Sheet material.....	24S-T3, Clad 24S-T3, Clad 24S-T6, and Clad 24S-T81			24S-T3, Clad 24S-T3, Clad 24S-T6, and Clad 24S-T81				Clad 24S-T3		24S-T3, Clad 24S-T3, Clad 24S-T6, and Clad 24S-T81			24S-T3			
$t^a$ \ D	1/8	5/32	3/16	1/8	5/32	3/16	1/4	1/8	5/32	3/16	1/8	5/32	3/16	1/8	5/32	3/16
0.032.....								*267								
0.040.....	217			227				*276	*441		265				*382	
0.051.....	258	*350		255	*415			*302	*471	*605	330	*542		361	*567	
0.064.....	305	350	*433	348	415	*615		329	*504	*654	405	575	*630	412	*602	*800
0.072.....	338	390	444	395	480	*615		399	*499	*699	440	630	*690	435	623	*847
0.081.....	374	440	446	415	560	615	*965		*537	*739	472	680	760	435	677	*908
0.091.....		505	590		625	727	*965		*620	869		735	855	435	725	*915
0.102.....		585	755		635	917	965			926		788	990	435	725	984
0.125.....		605	875		635	917	1,600			969		788	1,065			1,010

## YIELD STRENGTHS

0.032.....								112								
0.040.....	155			162				154	144		207			130		
0.051.....	205	210		241	185			196	221	207	322	276		277	217	
0.064.....	250	290	229	327	305	122		243	246	218	397	483	368	344	323	185
0.072.....	270	340	315	380	374	300		304	275	234	430	550	450	372	470	349
0.081.....	288	393	410	415	455	506	280		332	432	465	610	530	382	515	490
0.091.....		457	508		546	670	505		410	627		680	690	386	612	518
0.102.....		521	634		635	752	740			674		735	840	435	612	752
0.125.....		605	875		635	860	1,090			821		735	1,045			890

<sup>a</sup> Sheet gage is that of the upper sheet.

In cases where the lower sheet is thinner than the upper the shear-bearing allowable for the lower sheet-rivet combination should be computed.

Yield values of the sheet-rivet combinations marked thus (\*) are less than 3/4 of the indicated ultimate values.

Other sheet-rivet combinations may be used subject to specific approval of the procuring or certifying agency.

3.6114 *Hollow-end rivets.* If hollow-end rivets with solid cross-sections for a portion of the length (AN450) are used, the strength of these rivets may be taken equal to the strength of solid rivets of the same material, provided that the bottom of the cavity is at least 25 percent of the rivet diameter from the plane of shear, as measured toward the hollow end, and further provided that they are used in locations where they will not be subjected to appreciable tensile stresses.

3.6115 *High-shear rivets.* Allowable loads for high-shear steel rivets are given in section 2.6114. These rivets may be used in aluminum alloy materials.

3.6116 *Lockbolts and lockbolt stumps.* Lockbolts and lockbolt stumps shall be installed in conformance with the lockbolt manufacturer's recommended practices, and shall be inspected in accordance with procedures recommended by the manufacturer or by an equivalent method. The ultimate allowable shear and tensile strengths for protruding and flush head Huck lockbolts and lockbolt stumps are contained in table 3.6116. These strength values were established from test data and are minimum values guaranteed by the manufacturer. Yield shear and tensile strengths and ultimate and yield bearing strengths will be added when available.

Table 3.6116. *Ultimate Single Shear and Tensile Strengths of Protruding and Flush Head Huck Lockbolts<sup>a</sup> and Lockbolt Stumps (Pounds)*

Lockbolt pin material	Heat-treated Alloy steel		75S-T6	
	24S-T4		61S-T6	
Diameter (in.)	Loading		Single shear	Tension
	Single shear	Tension		
3/16 <sup>b</sup>	2,620	2,210	1,330	1,375
1/4 <sup>b</sup>	4,650	4,080	2,280	2,535
5/16	7,300	6,500	3,620	4,025
3/8	10,500	10,100	5,270	6,275

<sup>a</sup> Lockbolts are pull gun driven, lockbolt stumps are hammer or squeeze driven.

<sup>b</sup> Heat treated alloy steel Huck pull type lockbolts are available only in 3/16- and 1/4-inch diameters. Heat treated alloy steel Huck lockbolt stumps are available in 3/16-, 1/4-, 5/16-, and 3/8-inch diameters.

### 3.612 *Welded joints*

3.6121 *Fusion welds.* Since fusion welding is not generally used in the joining of major structural parts made of aluminum alloy, no values for allowable stresses for such joints will be given.

Fusion welding, however, is used on certain parts; e. g., fuel and oil tanks. The design of these parts is substantiated in part by special tests specified or deemed suitable by the procuring or certifying agency.

3.6122 *Spot welding.* The permissibility of the use of spot welding on structural parts is governed by the requirements of the procuring or certifying agency. Design shear strength allowables for spotwelds in various aluminum alloys are given in table 3.6122 (a). Table 3.6122 (b) gives the minimum allowable edge distance for the spotwelds in aluminum alloys; these values may be reduced for nonstructural applications, or for applications not depended upon to develop the full tabulated weld strength. Combinations of alloys suitable for spot welding are given in table 3.6122 (c). The thickness ratio of the thickest sheet to the thinnest outer sheet in the combination should not exceed 3.1.

3.61221 *Reduction in tensile strength of parent metal due to spotwelding.* In applications of spotwelding where ribs, intercostals, or doublers are attached to sheet, either at splices or at other

Table 3.6122 (a). *Spotweld Maximum Design Shear Strength Standards for Bare and Clad Aluminum Alloys<sup>1</sup>*

Nominal thickness of thinner sheet (inch)	Material ultimate tensile strength above 56 ksi <sup>2</sup>	Material ultimate tensile strength 28 ksi to 56 ksi <sup>3</sup>	Material ultimate tensile strength 20 ksi to 27.5 ksi <sup>4</sup>	Material ultimate tensile strength 19.5 ksi and below <sup>5</sup>
	Pounds	Pounds	Pounds	Pounds
0.012	60	52	24	16
0.016	86	78	56	40
0.020	112	106	80	62
0.025	148	140	116	88
0.032	208	188	168	132
0.040	276	248	240	180
0.051	384	354	329	240
0.064	552	500	451	320
0.072	678	589	524	364
0.081	842	691	620	424
0.091	1,020	810	703	484
0.102	1,230	960	760	548
0.114	1,465	1,085	803	591
0.125	1,698	1,300	840	629
0.156	2,400			

<sup>1</sup> Spotwelding of aluminum alloy combinations conforming to AN-A-11, AN-A-12, and QQ-A-245 may be accomplished providing specific approval is obtained from the procuring or certifying agency.


<sup>2</sup> Heat-treated and aged 14S, heat-treated 17S and 24S, heat-treated and rolled 24S, heat-treated and aged 75S and R-301, R-303.

<sup>3</sup> 52S-H34, 52S-H38, heat-treated and aged 53S and 61S.

<sup>4</sup> 2S-H18, 3S-H14, 61S annealed, 61S-T4, 52S annealed.

<sup>5</sup> 2S annealed, 2S-H14, 3S annealed.

Table 3.6122 (b) Minimum Edge Distances for Spotweld Joints

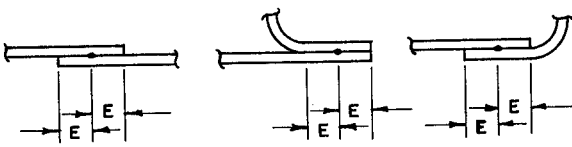

Thickness thinner sheet (inch)	Edge distance $E$	Thickness thinner sheet (inch)	Edge distance $E$
0.016	$\frac{3}{16}$	0.060	$1\frac{1}{32}$
0.020	$\frac{3}{16}$	0.070	$\frac{3}{8}$
0.025	$\frac{7}{32}$	0.080	$1\frac{1}{32}$
0.030	$\frac{1}{4}$	0.090	$\frac{1}{16}$
0.035	$\frac{1}{4}$	0.100	$\frac{1}{16}$
0.040	$\frac{9}{32}$	0.120	$\frac{1}{2}$
0.045	$\frac{5}{16}$	0.125	$\frac{9}{16}$
0.050	$\frac{5}{16}$	0.157	$\frac{3}{8}$

Intermediate gages will conform to the requirement for the next thinner gage shown.

For edge distances less than those specified above, appropriate reductions in the spotweld allowable loads shall be made. These reductions shall be subject to approval by the procuring or certifying agency.

points on the sheet panels, the allowable ultimate tensile strength of spotwelded sheet shall be determined by multiplying the "A" value for ultimate tensile sheet strength obtained from tables 3.111 by the appropriate efficiency factor shown on figure 3.61221.

Allowable ultimate tensile strengths for spotwelded sheet gages of less than 0.020 inch shall be established on the basis of tests acceptable to the procuring or certifying agency.

3.6123 *Aluminum brazing.* No values for allowable stresses in shear are given for joints made with this process. Allowables used in the design of parts made by this process are subject to substantiation by special tests in accordance with the requirements of the procuring or certifying agency.

3.613 *Adhesive bonded joints.* Joints may in some instances be made to advantage by the use of an adhesive suitable for the structural bonding of metals. This subject is discussed in reference 2.614.

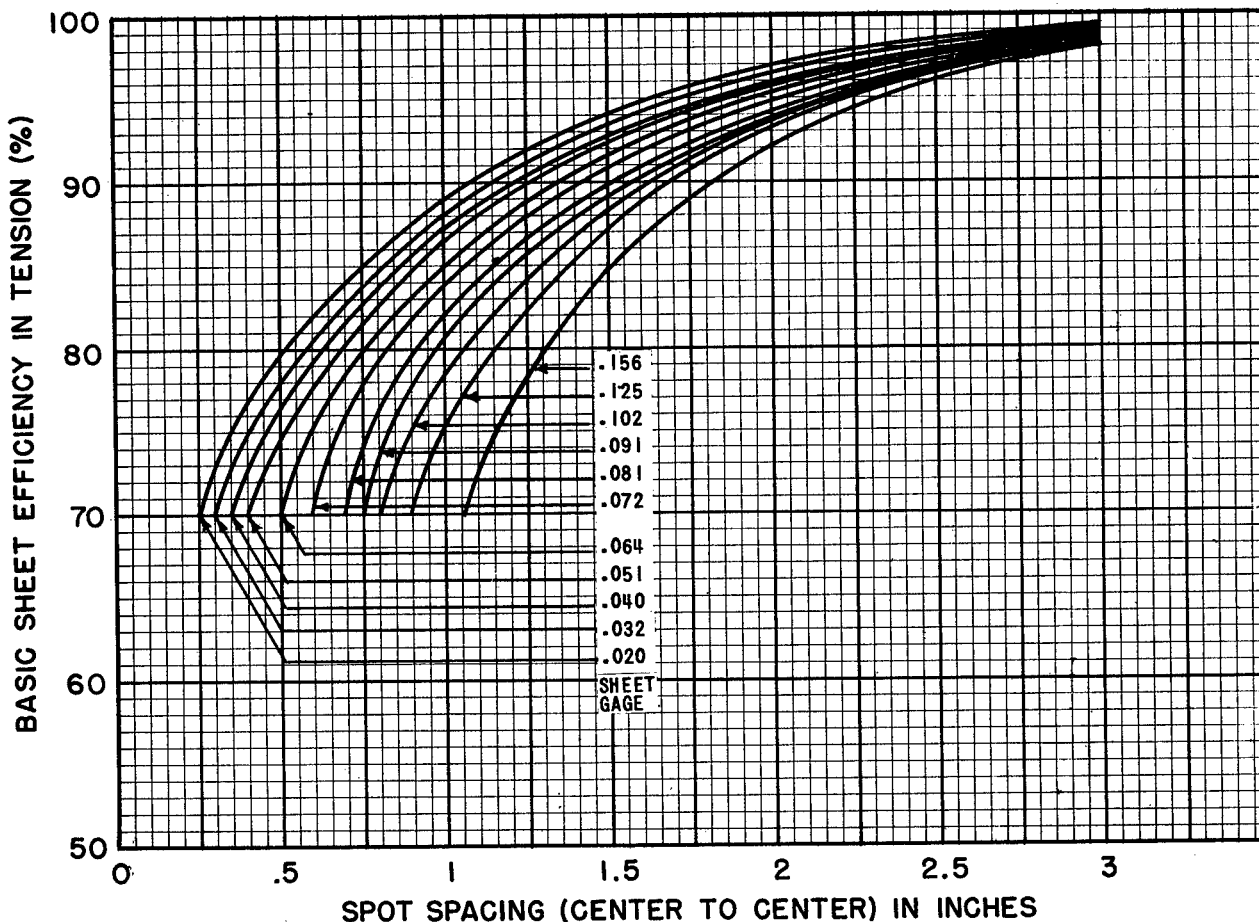


Figure 3.61221. Efficiency of the parent metal in tension for spotwelded aluminum alloys

Table 3.6122 (c). Acceptable Aluminum and Aluminum Alloy Combinations<sup>1</sup> for Spotwelding

Specification No.	Material	Specification No.	Material
QQ-A-315	(52S)	QQ-A-315	(52S)
QQ-A-318	(52S)	QQ-A-318	(52S)
QQ-A-327	(61S)	QQ-A-327	(61S)
QQ-A-331	(53S)	QQ-A-331	(53S)
QQ-A-354	(Bare 24S) <sup>2</sup>	QQ-A-354	(Bare 24S) <sup>2</sup>
QQ-A-355	(Bare 24S) <sup>2</sup>	QQ-A-355	(Bare 24S) <sup>2</sup>
QQ-A-359	(3S)	QQ-A-359	(3S)
QQ-A-362	(Clad 24S)	QQ-A-362	(Clad 24S)
QQ-A-411	(2S)	QQ-A-411	(2S)
QQ-A-561	(2S)	QQ-A-561	(2S)
AN-A-10	(Clad 75S) R303 <sup>3</sup>	AN-A-10	R303 (Clad 75S) <sup>3</sup>
AN-A-11	(Bare 75S) R303 <sup>2</sup>	AN-A-11	R303 (Bare 75S) <sup>2</sup>
AN-A-12	(Bare 24S) <sup>2</sup>	AN-A-12	(Bare 24S) <sup>2</sup>
QQ-A-362a	(Clad 24S)	QQ-A-362a	(Clad 24S)
QQ-A-245	(R301, Clad 14S)	QQ-A-245	(R301, Clad 14S)
QQ-A-261 and QQ-A-266	(Bare 14S) <sup>2</sup>	QQ-A-261 and QQ-A-266	(Bare 14S) <sup>2</sup>

<sup>1</sup> Aluminum alloys. The various aluminum and aluminum alloy materials referred to in this table may be spotwelded in any combinations except the combinations indicated by the asterisk (\*) in the table. The combinations, indicated by the asterisk (\*), may be spotwelded only with the specific approval of the procuring or certifying agency.

<sup>2</sup> The above table applies to construction of land- and carrier-based aircraft only. The welding of bare, high-strength alloys in construction of seaplanes and amphibians is prohibited unless specifically authorized by the procuring or certifying agency.

<sup>3</sup> Clad heat-treated and aged 75S material in thicknesses less than 0.020 inch shall not be welded without specific approval of the procuring or certifying agency.

## CHAPTER 4

# MAGNESIUM ALLOYS

### 4.1 General properties

#### 4.11 NORMAL (ROOM) TEMPERATURE PROPERTIES

4.111 *Design mechanical properties.* The design mechanical properties at normal (room) temperature for various magnesium alloys are listed in tables 4.111. The values in tables 4.111 have been derived from test data and are the minimum values expected but are not necessarily covered by procurement specifications.

The effects of notches, holes, and stress raisers on the static properties of magnesium alloys (see sec. 1.526) are given in references 4.111 (a) through (c).

4.112 *Fatigue properties.* Rotating beam, repeated flexure, and direct tension and compression strength data, for several magnesium alloy materials are given in tables 4.112. In using these data it should be remembered that they have been obtained from specimens in which stress concentrations are purposely minimized, and that suitable allowance should be made for reentrant corners, notches, holes, joints, and all other conditions which may produce localized high stresses. These localized high stresses, which have almost no effect on the static strength of the members, are of great importance in studying the effect of repeated stresses.

The values given in table 4.112 (a) were determined by testing 0.3-inch diameter machined and polished specimens (die cast were cast to shape) in R. R. Moore rotating beam fatigue machines and represent extreme fiber stresses which such specimens will withstand.

The values given in table 4.112 (b) were determined by testing 0.25-inch thick cast and forged specimens and 0.064-inch thick sheet specimens in Krouse plate bending fatigue machines and represent the completely reversed stresses that such specimens will withstand. Sand-cast specimens were machined; all other specimens received no special surface treatment. The values given in table 4.112 (c) were determined by testing 0.064-inch by 1-inch sheet specimens and 0.3-inch diameter machined and polished specimens in Krouse direct tension-compression fatigue machines, and represent uniformly distributed stresses which such specimens will withstand under repeated axial loads. The data presented in this table show a mean stress with a superimposed alternating stress, instead of maximum and minimum values. It also indicates the magnitude of the alternating stress that is expected to cause failure in conjunction with various mean stresses for various numbers of cycles.

Table 4.111 (a). Design Mechanical Properties of Magnesium Alloy Sheet, Tubes, and Shapes (Kips Per Square Inch)

Type.....	Sheet		Round tubing		Shapes (except hollow)				
	M-1		M-1		AZ80A				
	Q-Q-M-44	Q-Q-M-54	W-W-T-825	W-W-T-825	AZ61A	M-1	AZ31B		
Alloy (ASTM designation).....	M-1		M-1		M-1				
Specification.....	Q-Q-M-44		W-W-T-825		A.N.-M-26				
Condition.....	As extruded		As extruded		As extruded				
Thickness.....	0.020 to 0.250		0.050 to 0.250		A.N.-M-25				
$F_{tu}$ <sup>a</sup> .....	32	39	36	34	40	44	47	29	34
$F_{ty}$ .....	15	29	16	16	22	27	30	17	20
$F_{cy}$ .....	12	24	11	10	14	25	28	8	11
$F_{su}$ .....	17	18	17	18	19	20	23	14	18
$F_{bru}$ ( $e/D=1.5$ ) <sup>b</sup> .....	50	58	45	48	45	48	---	36	36
$F_{brv}$ ( $e/D=2.0$ ).....	60	68	50	51	55	56	---	45	45
$F_{brv}$ ( $e/D=1.5$ ).....	29	43	23	23	28	36	---	23	23
$F_{brv}$ ( $e/D=2.0$ ).....	29	43	23	23	32	40	---	23	23
Percent $e$ .....	12	4	7	8	10	5	5	2	10
$E, E_c$ .....	6,500	6,500	6,500	6,500	6,500	6,500	6,500	6,500	6,500
$G$ .....	2,400	2,400	2,400	2,400	2,400	2,400	2,400	2,400	2,400
$W$ lb./in. <sup>3</sup> .....	0.0645	0.0645	0.0649	0.0645	0.0649	0.0635	0.0635	0.0635	0.0645
Commercial designations.....	FSI-0 AMC52S-0	FS-1h	J-1 AMC57S	FS-1 AMC52S	J-1 AMC57S	M AM3S	O-1A AMC58S -T5	M AM3S	FS-1 AMC52S

<sup>a</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.  
<sup>b</sup>  $D$  = hole diameter;  $e$  = edge distance measured from the hole center line in the direction of stressing; use value of  $e/D=2.0$  for all larger value of edge distance; for ratios between 1.5 and 2.0 the bearing stress value should be obtained by linear interpolation; value for  $e/D$  less than 1.5 must be substituted by adequate tests prior to approval by the procuring or certifying agency.  
 \* Properties for sheet, round tubing and shapes, are taken parallel to the direction of rolling, drawing, or extrusion or maximum metal flow during fabrication.

Table 4.111 (b). Design Mechanical Properties of Magnesium Alloy Bars and Rods, Sand Castings and Forgings (Kips Per Square Inch)

Type	Bars and rods				Die <sup>a</sup> castings	Sand castings <sup>b</sup>				Forgings							
	AZ80A		AZ31B			AZ90		M-1		M1A		AZ61A		TA54A			
	AN-M-24	AN-M-25	AN-M-26	AN-M-27		AN-M-16	AN-M-20	AN-M-21	AN-M-22	AN-M-23	AN-M-20	AN-M-21	AN-M-22	AN-M-23			
Condt on	As extruded		Ex-truded, treated, and aged		As extruded		As cast		Heat-treated and aged		As cast		Heat-treated and aged				
	Composition A		Composition B		Composition C		As cast		Heat-treated and aged		As cast		Heat-treated and aged				
Th cknes	0.250 to 1.500																
	40	43	45	48	30	35	30	34	34	34	12	20	34	34	36		
$F_{ts}$	26	28	30	33	20	22	20	10	10	10	4	10	10	18	22		
$F_{ty}$	16	18	27	30	8	14	20	10	10	10	4	10	10	18	22		
$F_{ty}$	19	19	20	23	14	16	18	16	17	19	10	16	17	20	25		
$F_{ts}$	$F_{ts}$ ( $e/D=1.5$ ) <sup>c</sup>																
$F_{ty}$	$F_{ty}$ ( $e/D=2.0$ )																
$F_{ty}$	$F_{ty}$ ( $e/D=1.5$ )																
$F_{ty}$	$F_{ty}$ ( $e/D=2.0$ )																
Percent $\epsilon$	11	9	5	4	3	10	2	4	7	3	3	40	40	55	7		
$E, E_c$	6,500																
$G$	2,400																
$W$ lbs./in. <sup>3</sup>	0.0649		0.0653		0.0635		0.0653		0.0664		0.0635		0.0657		0.0649		
	J-1	O-1	O-1A	O-1HTA	M	FS-1	R	H-AC	H-HT	H-HTA	M-AC	C-AC	C-HT	C-HT	O-1	O-1A	M
Commercial designations	AM	AM	AM	AM	AM3S	AM	AM	AM	AM	AM	AM	AM	AM	AM	AM	AM	AM
	C57S	C58S	C58S-T5	C52S	263-C	265-T4	265C	265-T4	265-T6	403C	260C	260-T4	260-T6	C57S	C58S	C58S-T5	65S

<sup>a</sup> Properties given in this column are typical properties from material specification.  
<sup>b</sup> The sand casting properties are minimum values obtained from cast test bars. Reference should be made to the specific requirements of the procuring or certifying agency with regard to the use of the above values in the design of castings.  
<sup>c</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.  
<sup>d</sup>  $D$  = hole diameter;  $\epsilon$  = edge distance measured from the hole center line in the direction of stressing;  
 use value of  $e/D=2.0$  for all larger values of edge distance; for ratios between 1.5 and 2.0, the bearing stress value should be obtained by linear interpolation; values for  $e/D$  less than 1.5 must be substantiated by adequate tests prior to approval by the procuring or certifying agency.  
<sup>e</sup> Properties for bars and rods, and forgings are taken parallel to the direction of rolling, drawing, or extrusion or maximum metal flow during fabrication.

Table 4.112 (a). Rotating-Beam Fatigue Strength<sup>1</sup>

[Values given were determined by testing 0.3-inch diameter machined and polished specimens (die cast to shape) in R. R. Moore rotating-beam fatigue machines and represent extreme fiber stresses which such specimens will withstand in completely reversed flexure.]

Alloy and temper	Fatigue strength (reversed stress), ksi at indicated number of cycles			
	100,000 cycles	1,000,000 cycles	10,000,000 cycles	100,000,000 cycles
<b>Sand cast:</b>				
C-AC, AM260C	18.5	16.5	14.5	13.0
C-HT	20.0	18.0	16.5	16.0
C-HTS	20.5	17.5	15.0	13.0
C-HTA	19.5	17.5	16.0	15.0
H-AC, AM265C	18.0	14.0	10.5	10.5
H-ACS	23.0	19.0	15.0	12.0
H-HT	21.5	19.0	16.5	16.5
H-HTS	21.0	18.5	16.0	15.0
H-HTA	18.0	17.0	16.0	15.0
Die cast: R (c), AM263C	17.5	16.0	15.0	15.0
<b>Extruded:</b>				
M, AM3S	15.5	13.0	10.5	10.5
FS-1	27.0	24.0	21.0	19.0
J-1, AMC57S	24.5	22.5	20.5	20.0
O-1, AMC58S	27.0	24.5	22.5	20.5
O-1HTA and AMC58ST51	27.0	24.5	22.5	20.5
<b>Forged:</b>				
J-1	27.5	24.5	21.5	19.5
O-1	28.0	25.0	22.0	19.5
O-1A	25.0	22.5	20.0	18.0
O-1HTA	26.0	21.0	16.0	16.0

<sup>1</sup> Data based on tests conducted by the Dow Chemical Co. and American Magnesium Co.



Table 4.112 (b). Repeated-Flexure Fatigue Strength

[Values given were determined by using cast and forged 0.25-inch thick specimens, and 0.064-inch thick sheet specimens in Krouse plate bending fatigue machines, and represent the approximate reversed (alternating) stresses, *ksi*, that can be superimposed on the mean stresses for various numbers of cycles. Plus (+) means tension, minus (-) means compression.]

Alloy and temper	Mean stress <i>ksi</i>	Fatigue strength (reversed stress) <i>ksi</i> at indicated number of cycles		
		100,000 cycles	1,000,000 cycles	10,000,000 cycles
Sand cast and machined H-AC, H-HTS, H-HT, H-HTA, C-AC, C-HT, and C-HTA <sup>1</sup> -----	0	± 13.0 to ± 19.5	± 11.0 to ± 16.0	± 11.0 to ± 13.5
	+5	± 10.0 to ± 16.3	± 8.0 to ± 15.5	± 8.5 to ± 13.0
	+10	± 8.0 to ± 13.5	± 6.0 to ± 12.5	± 6.0 to ± 11.0
	+15	± 6.0 to ± 11.0	± 5.0 to ± 8.5	± 3.5 to ± 6.5
	0	± 10.5	± 9.0	± 8.0
Die cast R-----	0			
Extruded:				
M-----	0	± 14.0	± 11.0	± 10.0
O-1A-----	0	± 20.0	± 15.0	± 12.5
O-1HTA-----	0	± 19.5	± 16.0	± 13.0
J-1-----	0	± 17.5	± 12.0	± 11.5
Ma sheet-----	0	± 15.5	± 12.0	± 10.0
	+5	± 13.5	± 11.0	± 8.5
	+10	± 11.0	± 9.0	± 7.5
	+15	± 9.5	± 7.0	± 6.5
	+20	± 8.0	± 5.0	± 5.0
Mh sheet-----	0	± 18.5	± 14.0	± 11.0
	+5	± 18.0	± 13.0	± 11.0
	+10	± 16.0	± 12.5	± 11.0
	+15	± 14.5	± 11.0	± 10.0
	+20	± 13.0	± 10.0	± 9.0
FS-1a, sheet-----	0	± 15.5	± 15.0	± 14.5
	+5	± 15.0	± 13.5	± 13.5
	+10	± 14.5	± 12.5	± 12.5
	+15	± 13.0	± 11.5	± 11.5
	+20	± 10.5	± 9.5	± 8.5
FS-1h, sheet-----	0	± 18	± 16	± 15.5
	+5	± 18	± 15	± 14.5
	+10	± 18	± 14	± 14
	+15	± 16	± 13	± 13
	+20	± 15.5	± 11.5	± 11.5
Forged:				
M-----	0	± 13.0	± 9.0	± 6.0
O-1HTA-----	0	± 18.0	± 14.5	± 14.0
J-1-----	0	± 16.5	± 12.5	± 12.0

<sup>1</sup> Stress scatter bands for sand cast and machined alloys are applicable to all alloys listed, but the range of scatter for any particular alloy is not

necessarily as broad as the bands listed.

Data based on tests by the Dow Chemical Co.

Table 4.112 (c). Direct Tension-Compression Fatigue Strength\*

[Values given were determined by using 0.064- by 1-inch sheet specimens and 0.3-inch diameter machined and polished specimens in Krouse direct tension-compression fatigue machines and represent uniformly distributed stresses which such specimens will withstand under repeated axial loads. Stresses considered algebraically: plus (+) means tension minus (-) means compression.]

Alloy and temper	Mean (steady) stress, ksi	Reversed (alternating) stress, ksi at indicated number of cycles		
		100,000 cycles	1,000,000 cycles	10,000,000 cycles
Sand cast and machined H-AC, H-HTS, H-HT, H-HTA, C-AC, and C-HT*	0	± 17.5 to ± 21.5	± 15.0 to ± 19.0	± 12.0 to ± 17.5
	+5	± 14.0 to ± 17.5	± 12.0 to ± 17.0	± 10.0 to ± 16.0
	+10	± 11.5 to ± 15.0	± 9.5 to ± 14.5	± 8.0 to ± 14.0
	+15	± 9.0 to ± 13.0	± 7.5 to ± 10.0	± 6.0 to ± 12.0
Ma, sheet	0	± 9.0	± 6.0	± 6.0
	+5	± 8.5	± 6.0	± 6.0
	+10	± 8.0	± 5.5	± 5.0
	+15	± 7.0	± 5.0	± 5.0
	+20	± 6.5	± 4.5	± 4.5
Mh, sheet	0	± 17.0	± 14.0	± 14.0
	+5	± 15.0	± 12.0	± 12.0
	+10	± 13.0	± 10.0	± 10.0
	+15	± 11.5	± 8.0	± 8.0
	+20	± 9.5	± 6.0	± 6.0
FS-1a, sheet	0	± 10.5	± 8.5	± 8.0
	+5	± 9.5	± 8.0	± 7.5
	+10	± 9.5	± 7.5	± 7.0
	+15	± 8.0	± 7.0	± 7.0
	+20	± 7.0	± 6.5	± 6.5
FS-1h, sheet	0	± 14.5	± 14.0	± 14.0
	+5	± 12.5	± 12.0	± 12.0
	+10	± 11.0	± 10.0	± 10.0
	+15	± 9.0	± 8.0	± 8.0
	+20	± 7.0	± 6.0	± 6.0
O-1 HTA, extrusions	0	± 38.0	± 31.5	± 25.5
	+5	± 33.0	± 27.5	± 22.5
	+10	± 28.0	± 23.5	± 19.5
	+15	± 23.0	± 20.0	± 16.5
	+20	± 18.0	± 16.0	± 13.5
J-1, extrusions	0	± 17.5	± 13.5	± 13.5
	+5	± 15.0	± 11.5	± 11.5
	+10	± 13.0	± 9.0	± 9.0
	+15	± 11.0	± 7.0	± 7.0
	+20	± 9.0	± 5.0	± 5.0

\*NOTE.—See note 1 on table 4.112 (b).

Data based on tests by the Dow Chemical Co.

4.113 Typical stress-strain and tangent modulus data. Typical stress-strain diagrams and tangent

modulus values at various stresses are given in figure 4.113 for several magnesium alloy products.

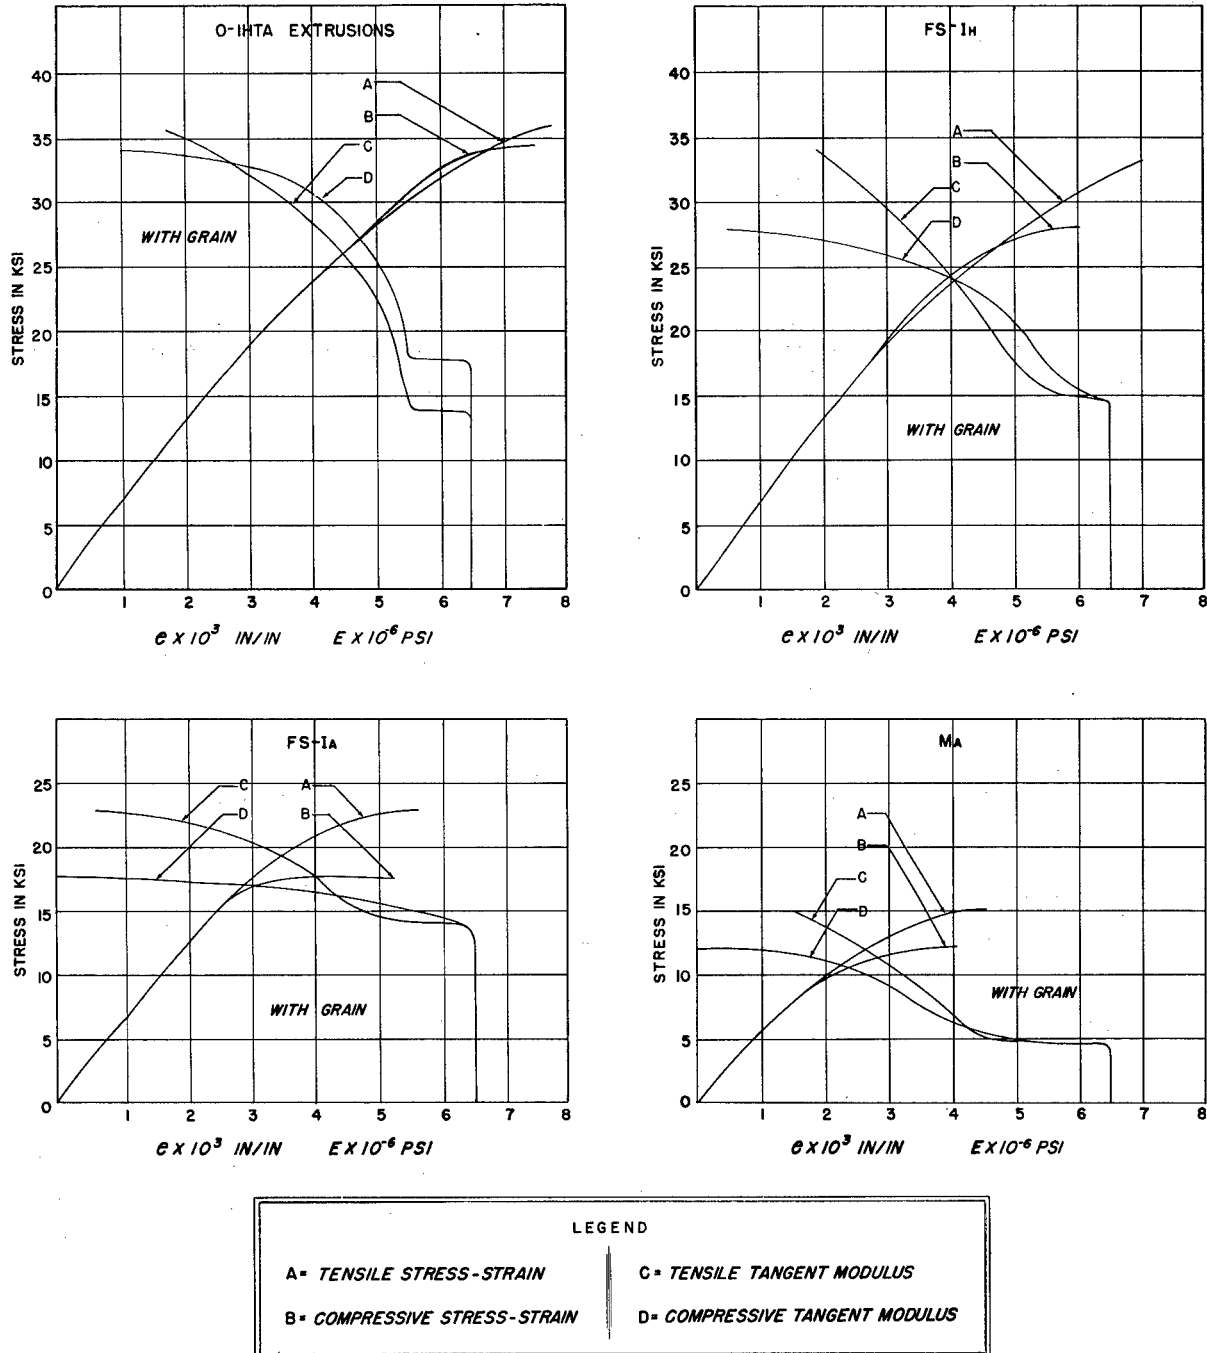


Figure 4.113 (a). Typical stress-strain and tangent modulus curves for magnesium alloy sheet and extruded shapes.

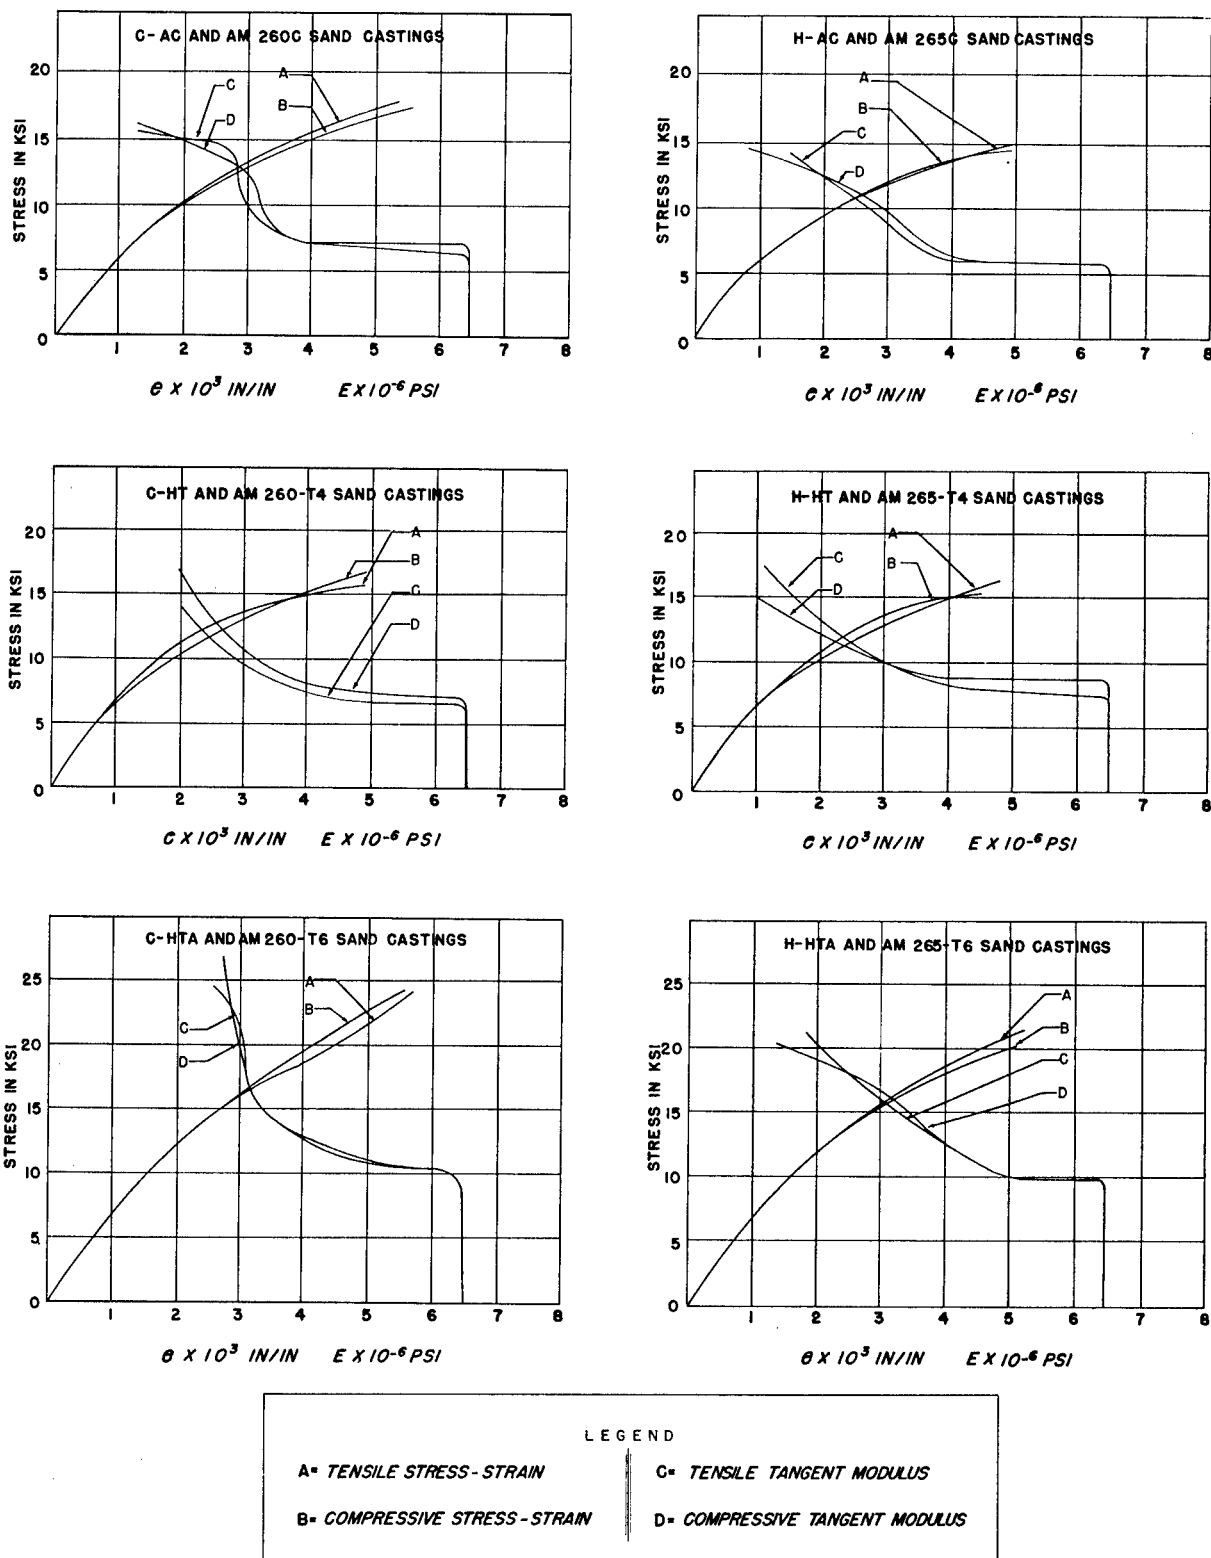


Figure 4.113 (b). Typical stress-strain and tangent modulus curves for magnesium alloy sand castings.

## 4.12 TEMPERATURE EFFECTS

### 4.121 *Low temperature*

### 4.122 *Elevated temperature*

4.1221 *Static properties.* Curves for computing the approximate reduction in tensile ultimate and tensile yield properties for magnesium alloys M, O-1HTA, AMC 58S-T51, and EM51-HTA, held unstressed at elevated temperature up to 600° F. for various time intervals and then tested statically at temperature, are given in figures 4.1221 (a) to 4.1221 (m). Available data indicates that the data in figures 4.1221 (a) to 4.1221 (m) may also be used to

determine approximate shear, bearing and compressive properties of magnesium alloys at elevated temperatures as follows:

(a) The percentages for tensile ultimate strength may also be applied to shear and bearing ultimate strengths.

(b) The percentages for tensile yield strength may be applied to compressive and bearing yield strengths.

Data are based on continuous heating but are considered applicable to intermittent heating when the total time at temperature is the same.

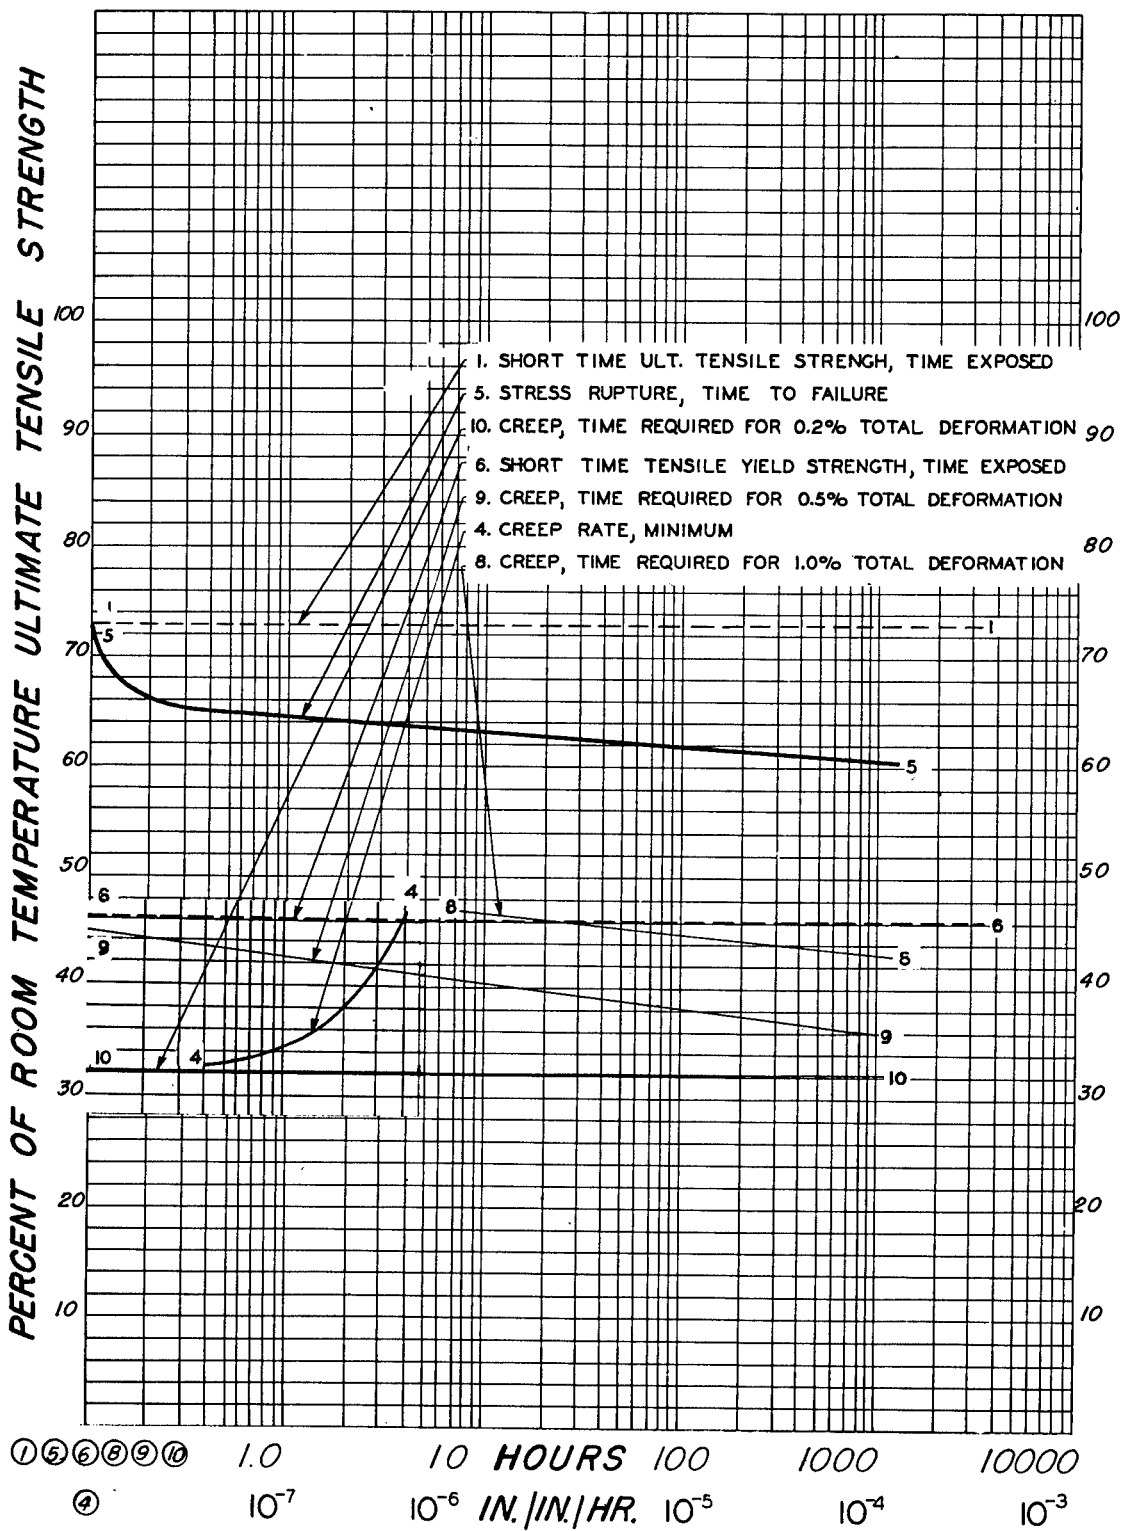


Figure 4.1221 (a). Elevated temperature properties of forged M (annealed 1 hour at 700° F.) magnesium alloy at 200° F. (tensile) (R. T.  $F_{tu}$  = 33,500 p. s. i.).

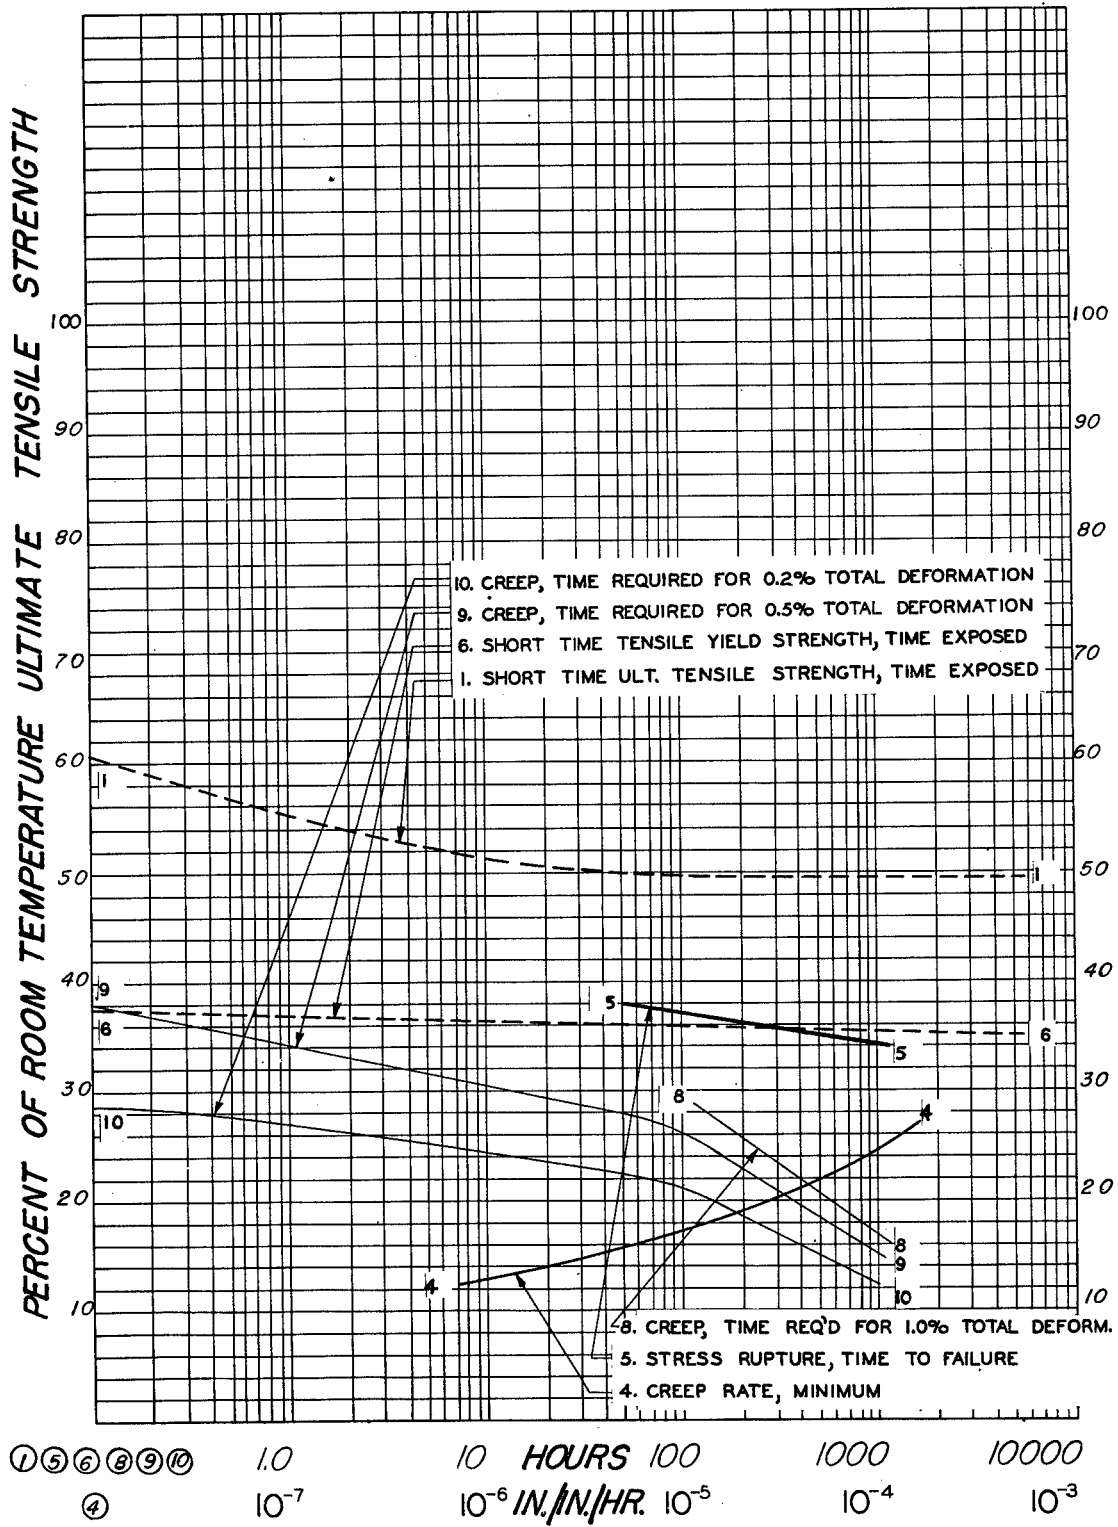


Figure 4.1221 (b). Elevated temperature properties of forged M (annealed 1 hour at 700° F.) magnesium alloy at 300° F. (tensile) (R. T.  $F_{tu} = 33,500$  p. s. i.).

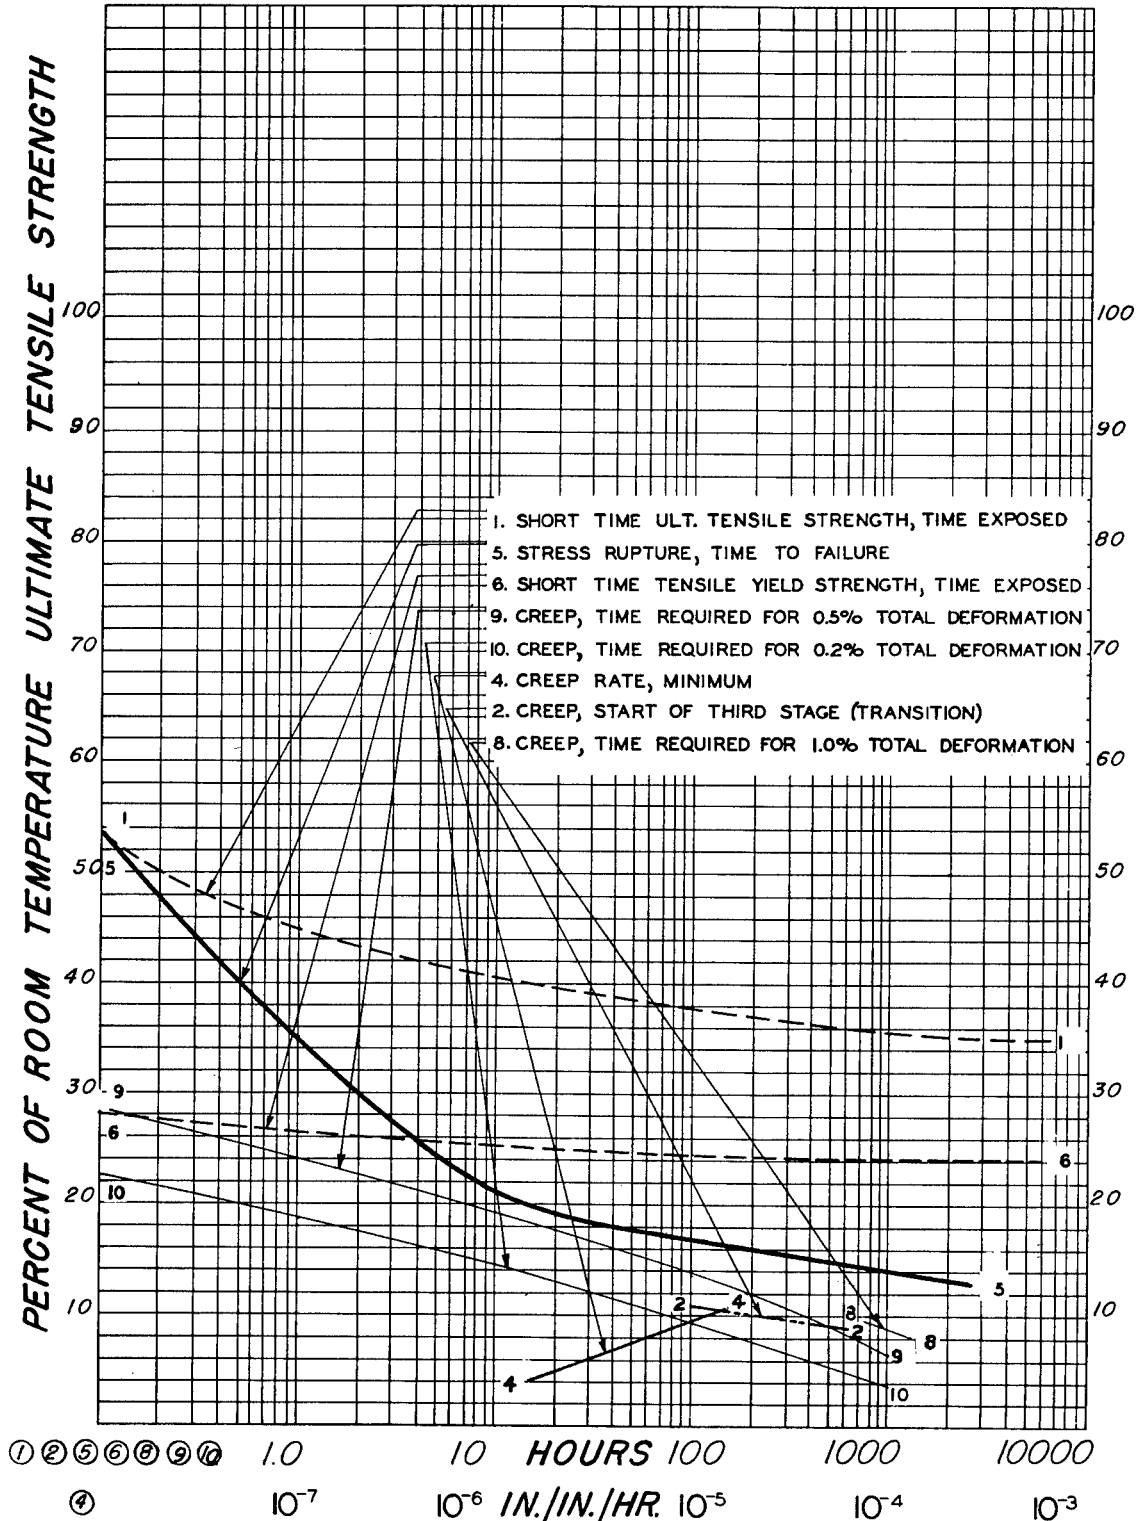


Figure 4.1221 (e). Elevated temperature properties of forged M (annealed 1 hour at 700° F.) magnesium alloy at 400° F. (tensile) (R. T.  $F_{tu} = 33,500$  p. s. i.).



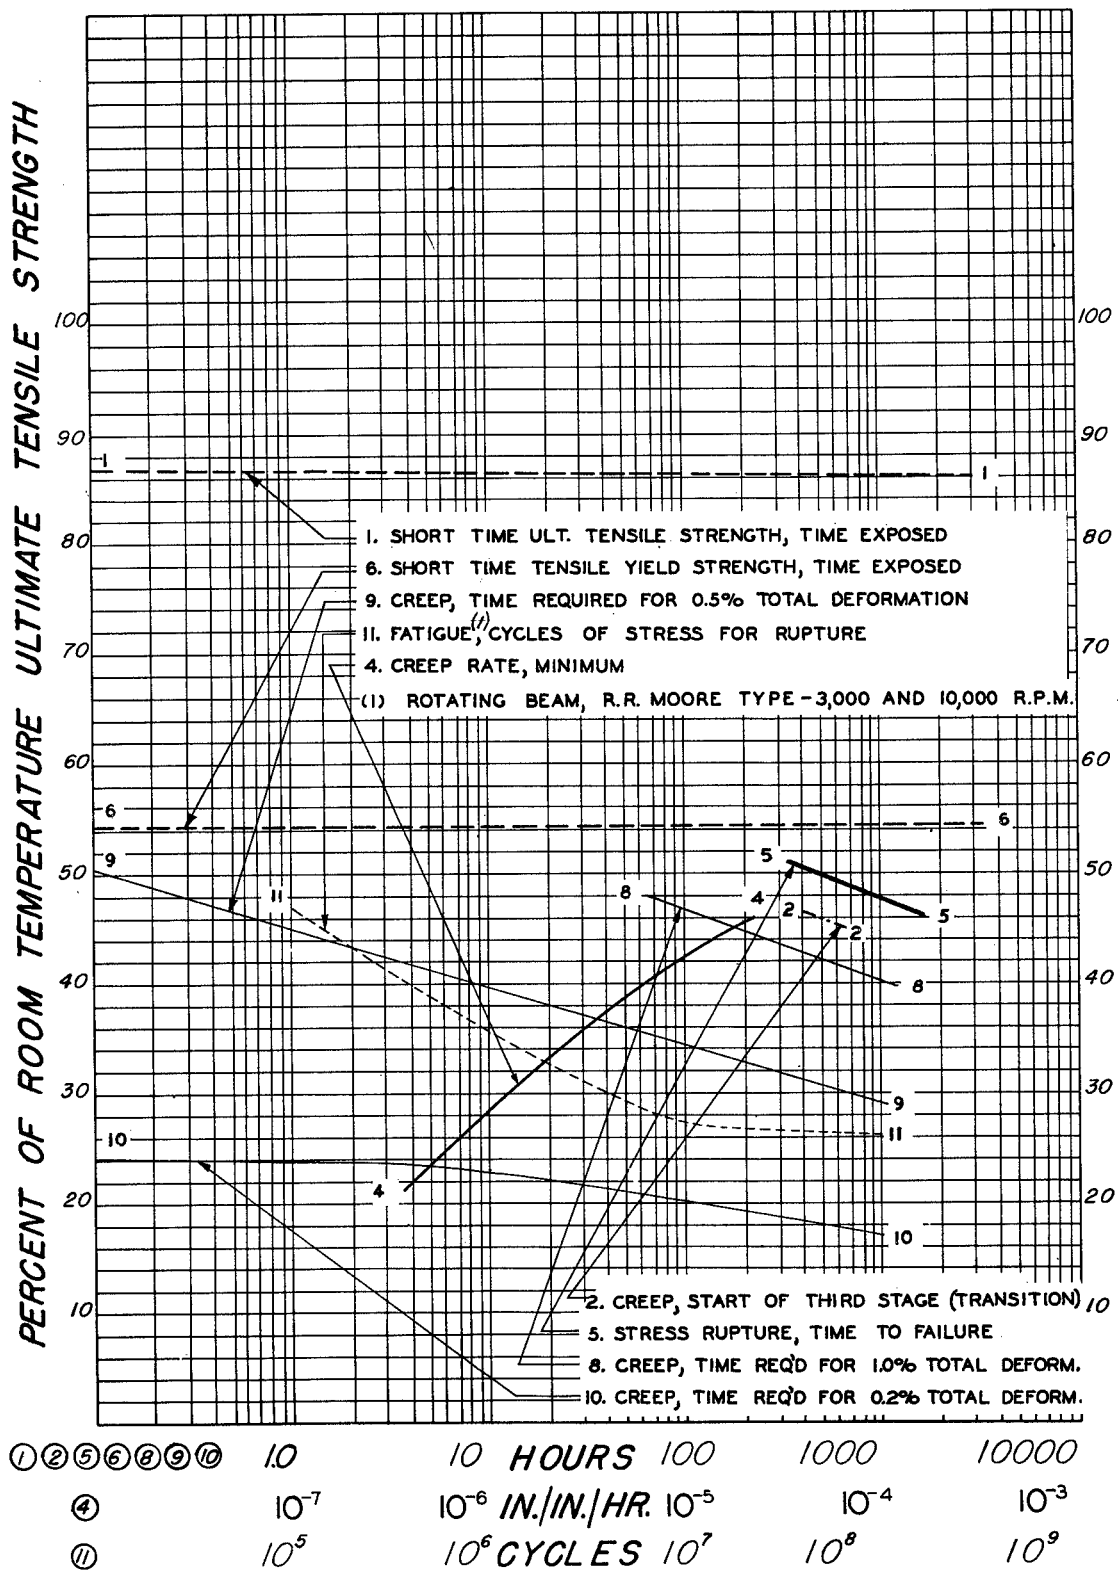


Figure 4.1221 (d). Elevated temperature properties of forged O-1HTA and AMC 58S-T51 magnesium alloy at 200° F. (tensile) (R. T.  $F_{tu} = 49,000$  p. s. i.).

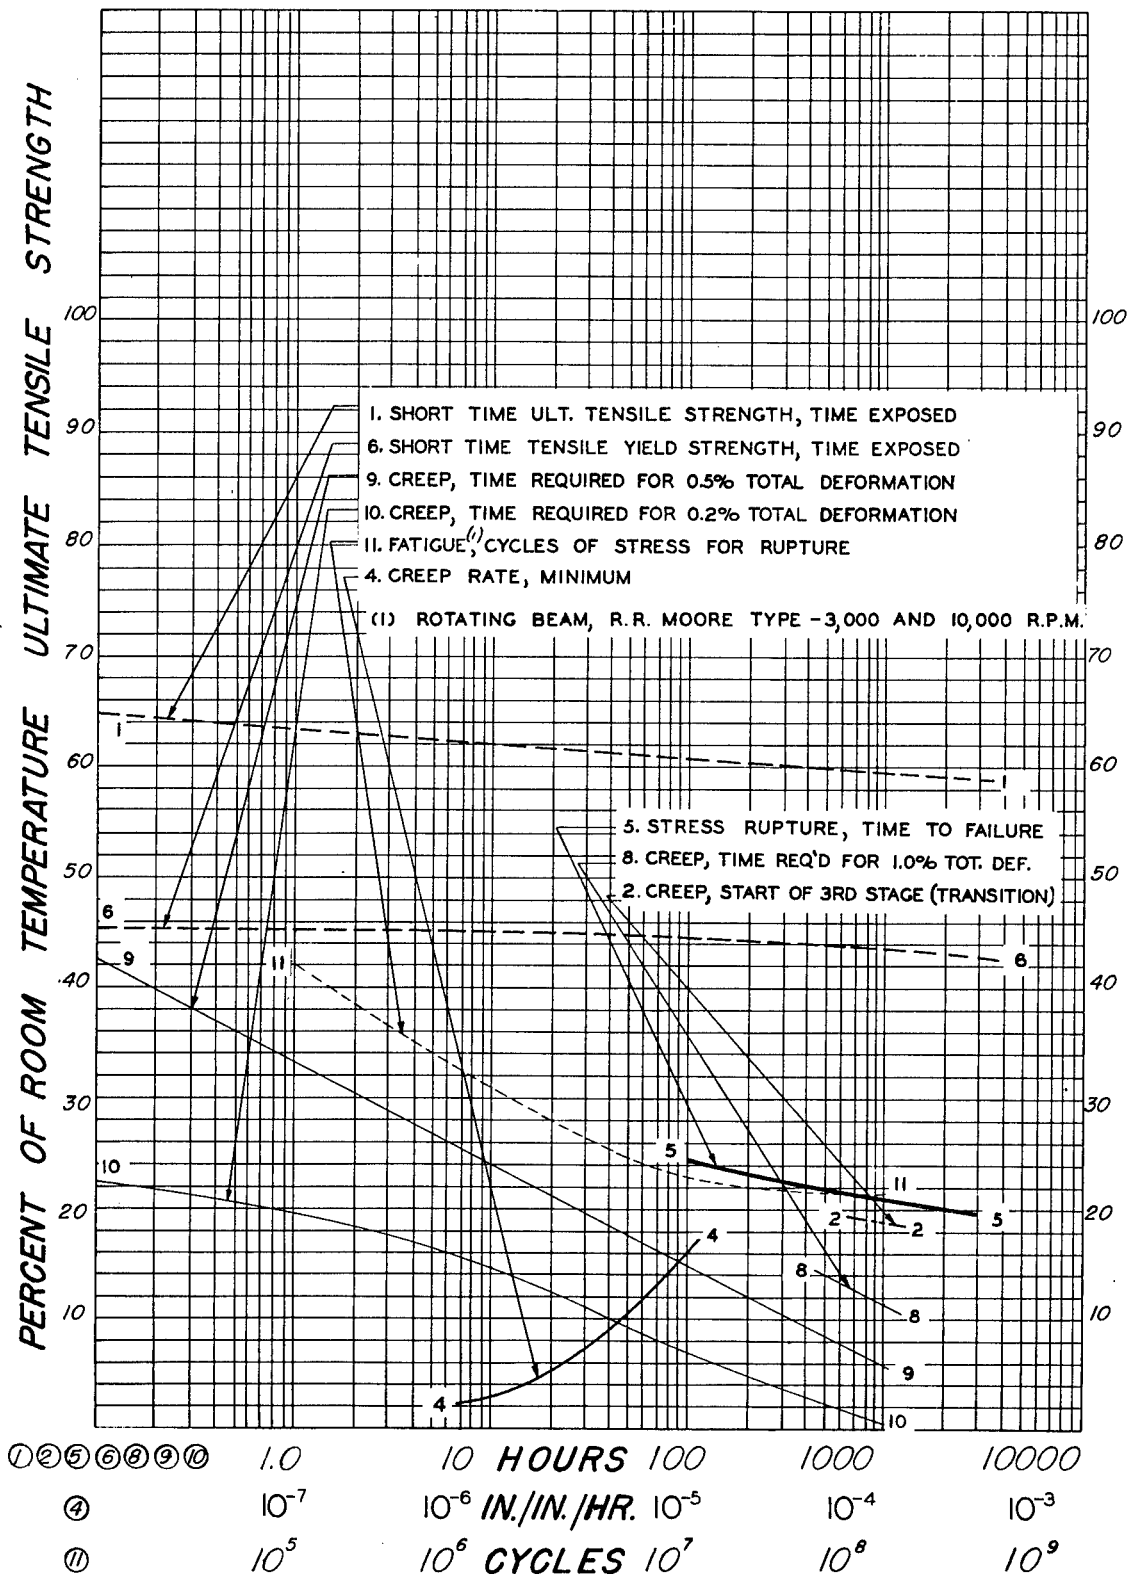


Figure 4.1221 (e). Elevated temperature properties of forged O-1HTA and AMC58S-T51 magnesium alloy at 300° F. (tensile) (R. T.  $F_{tu} = 49,000$  p. s. i.).

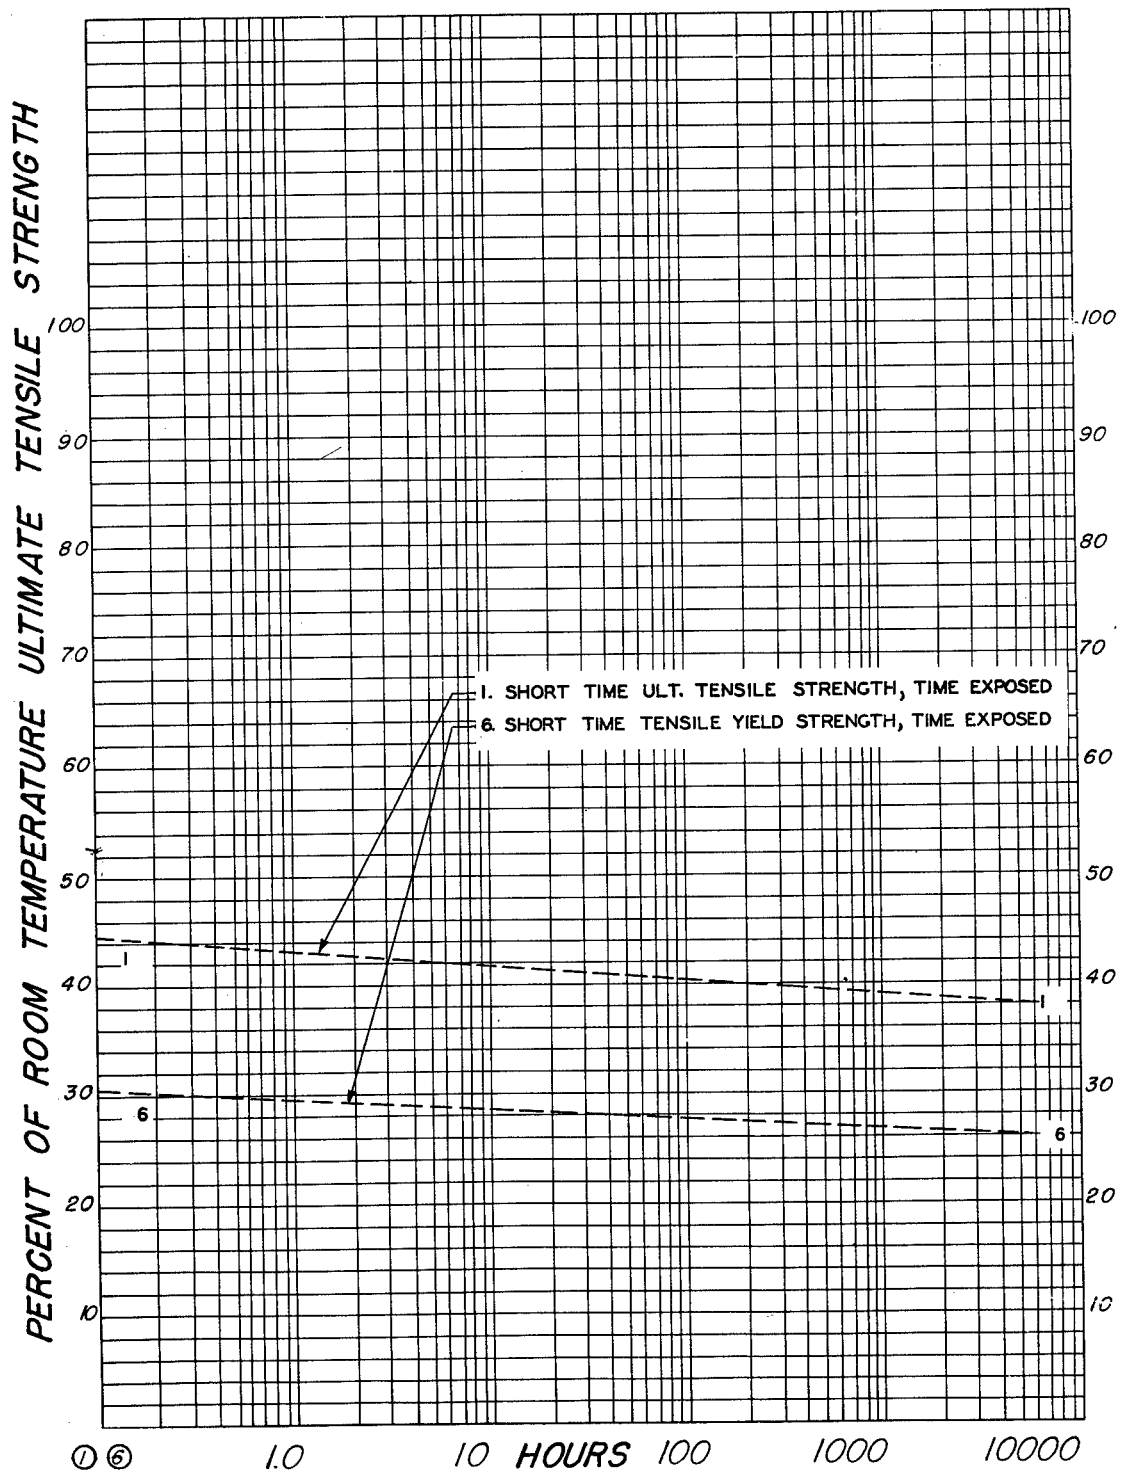


Figure 4.1221 (f). Elevated temperature properties of forged O-1HTA and AMC 58S-T51 magnesium alloy at 400° F. (tensile) R. T.  $F_{tu} = 49,000$  p. s. i.

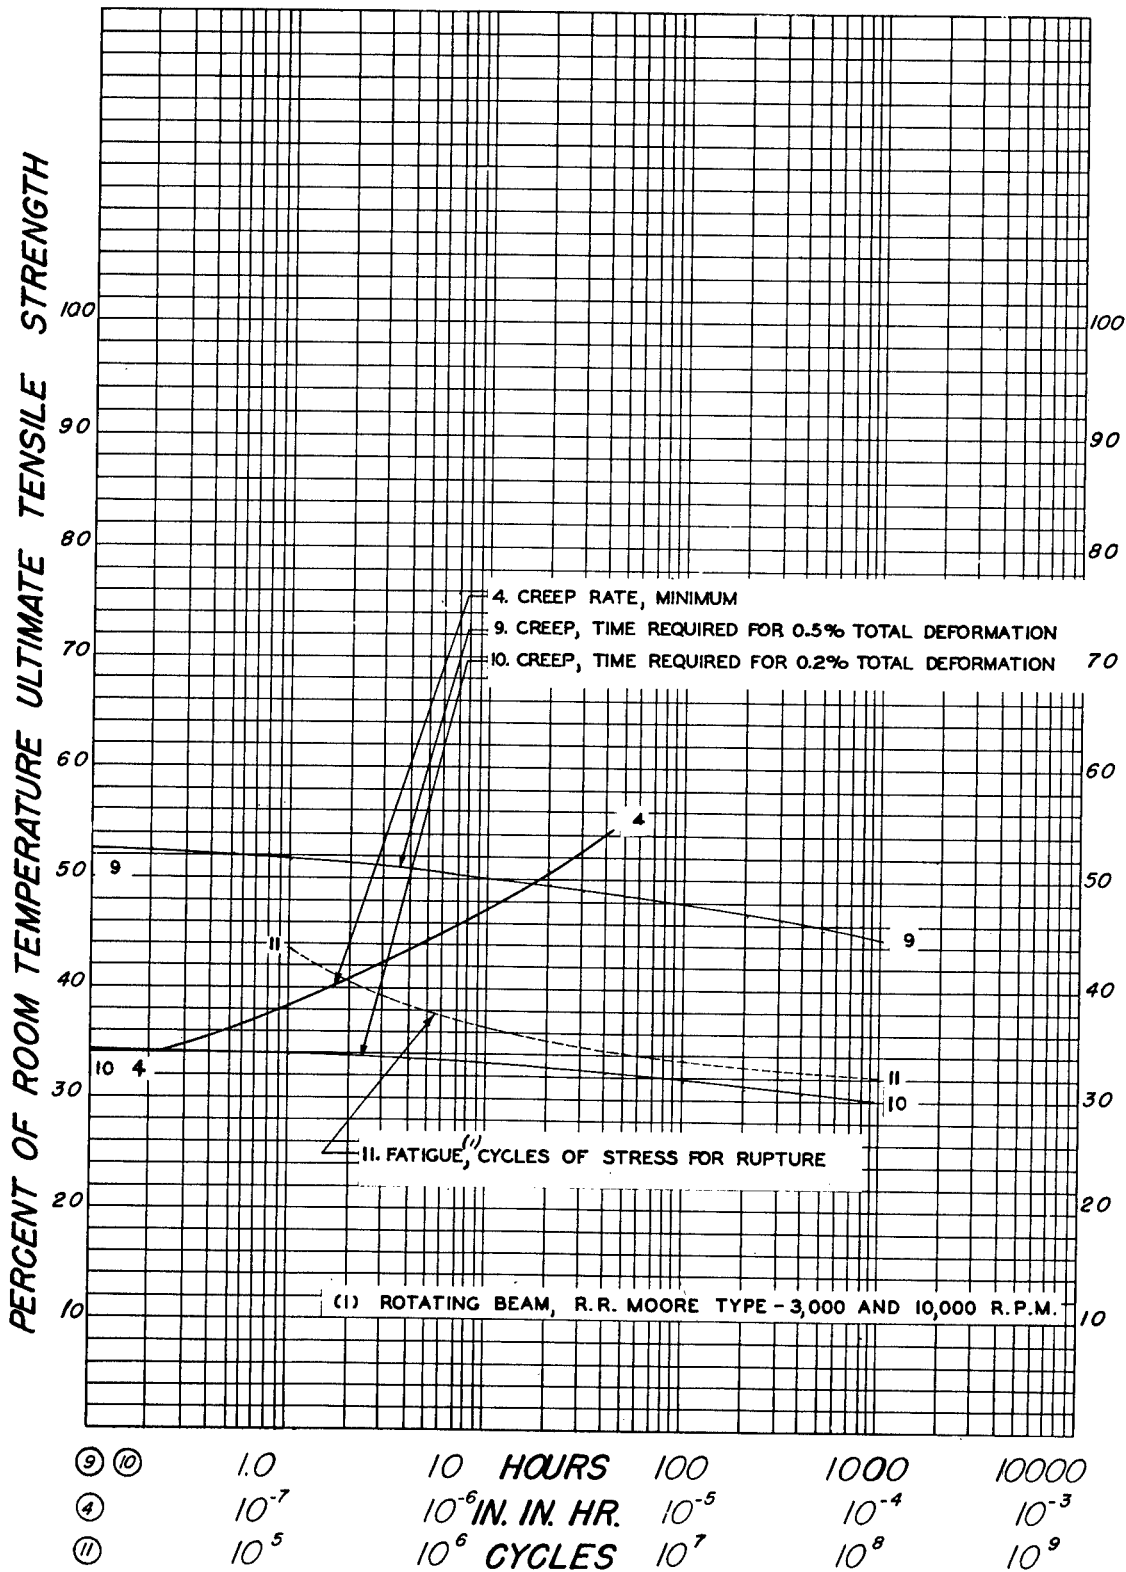


Figure 4.1221 (g). Elevated temperature properties of forged EM51-HTA magnesium alloy at 300° F. (tensile) (R. T.  $F_{tu} = 37,000$  p. s. i.).

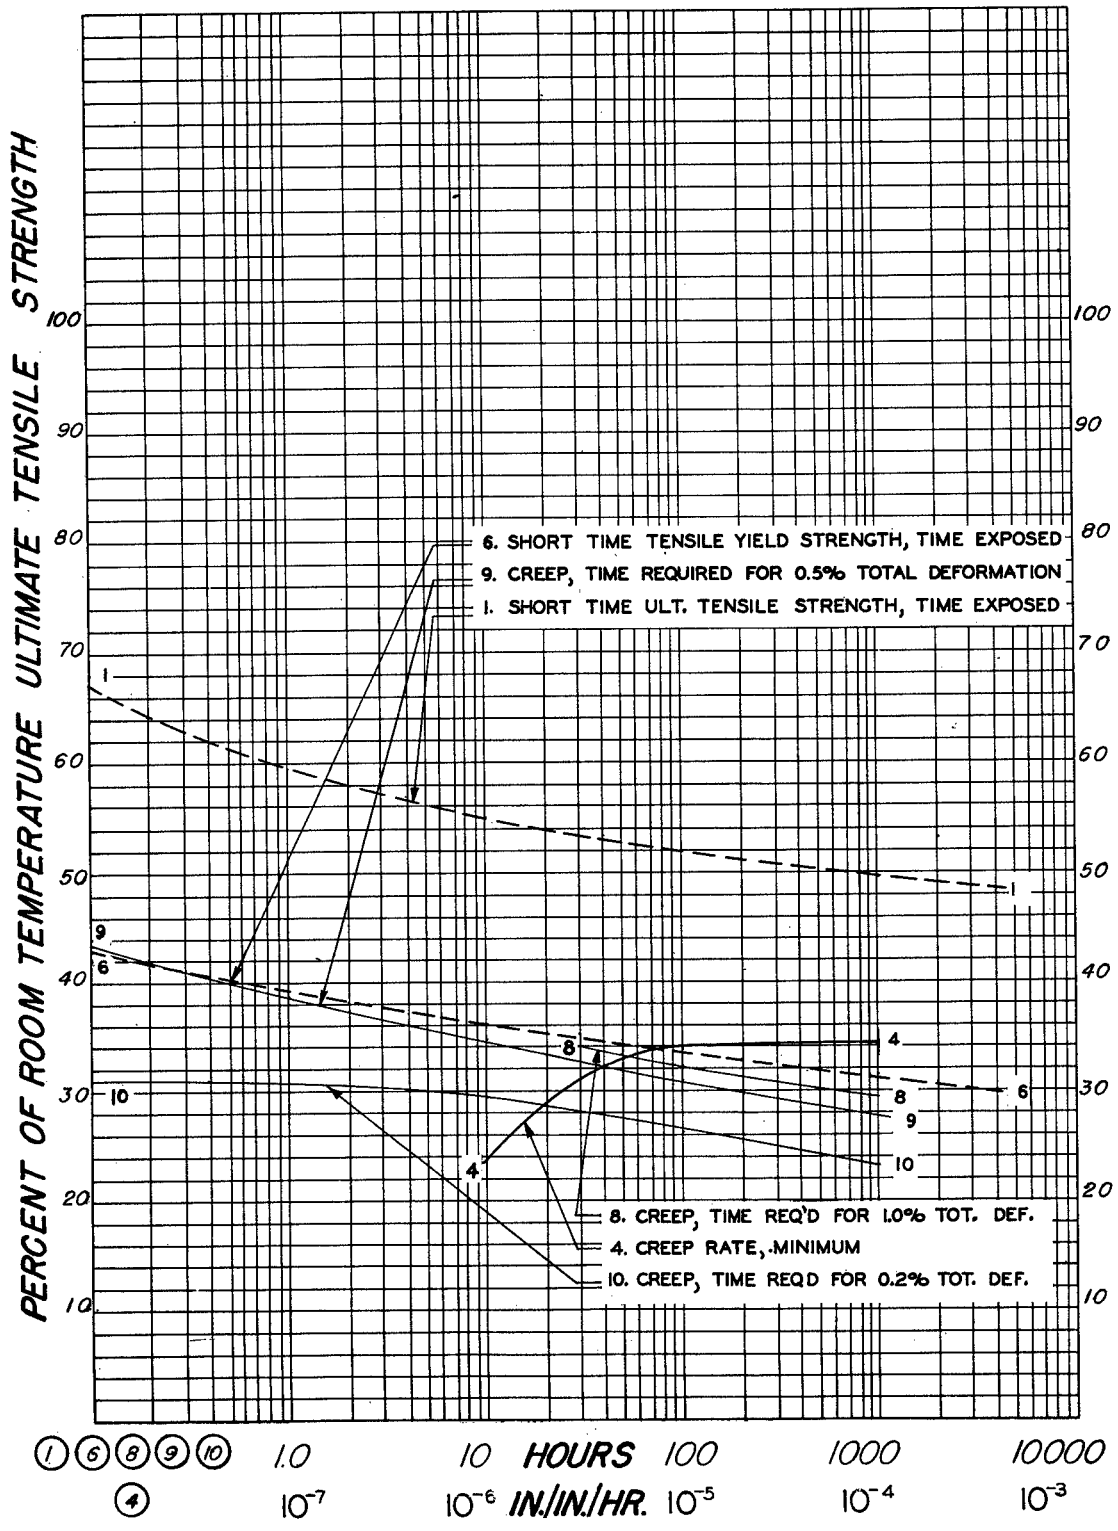


Figure 4.1221 (h). Elevated temperature properties of forged EM51-HTA magnesium alloy at 400° F. (tensile) (R. T.  $F_{tu}$  = 37,000 p. s. i.).

STRENGTH OF METAL AIRCRAFT ELEMENTS

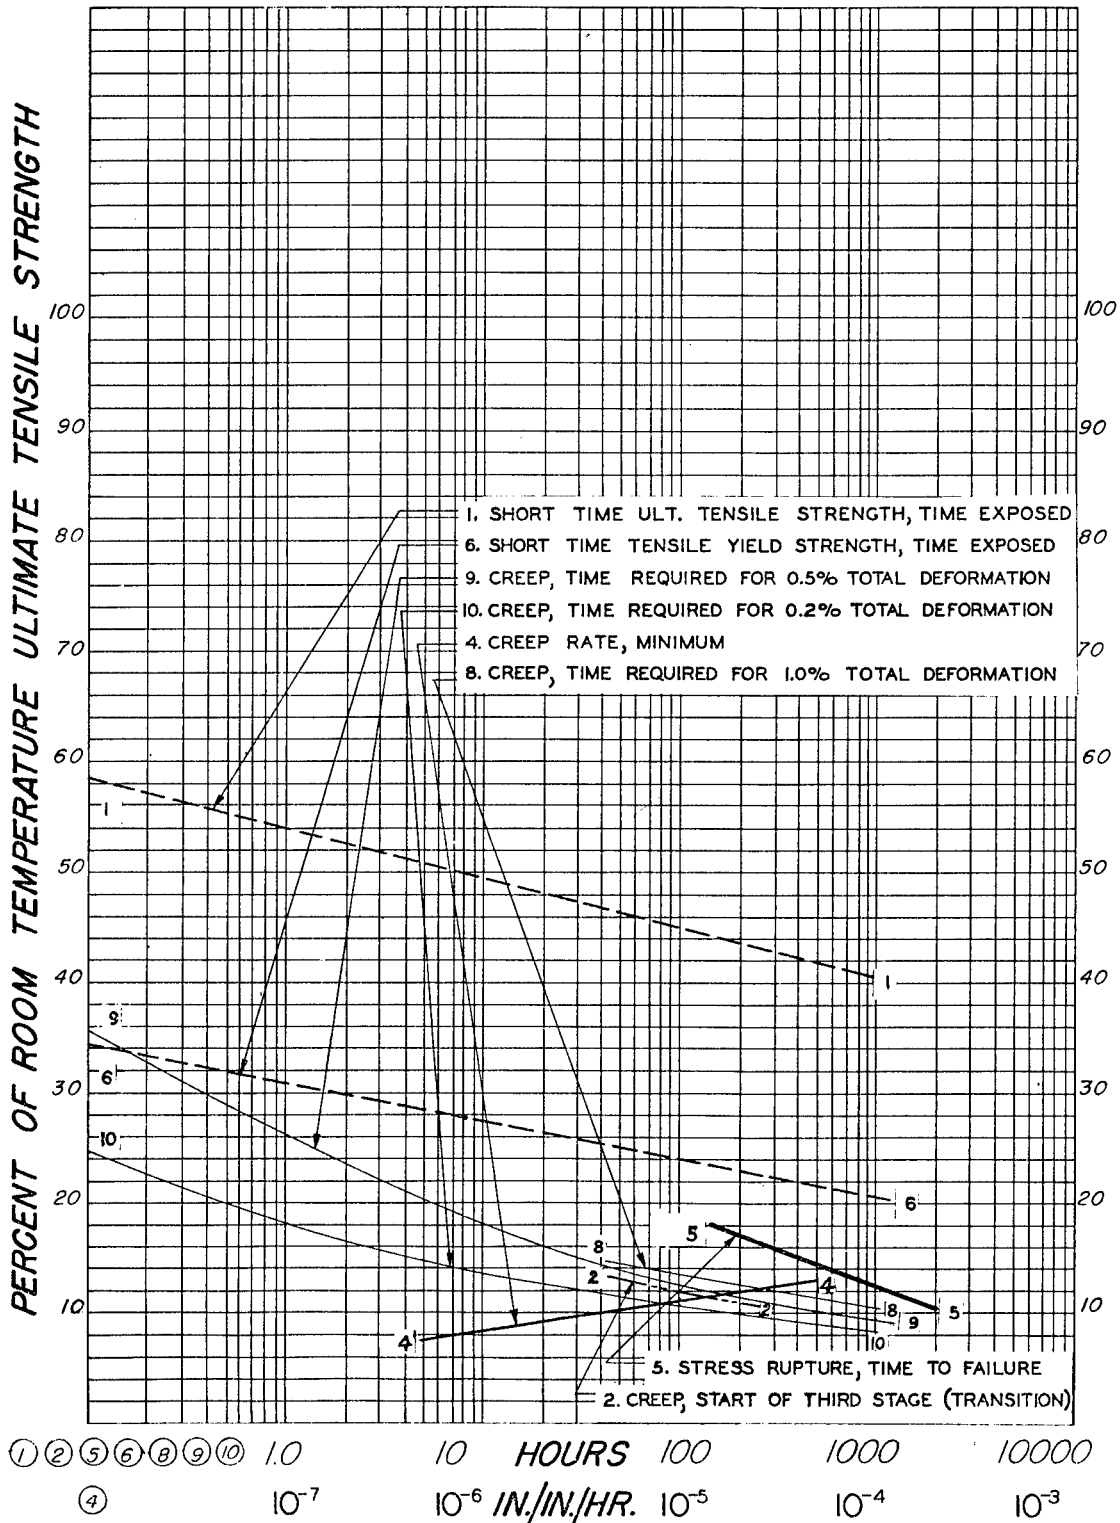


Figure 4.1221 (i). Elevated temperature properties of forged EM51-HTA magnesium alloy at 500° F. (tensile) (R. T.  $F_{tu} = 37,000$  p. s. i.).

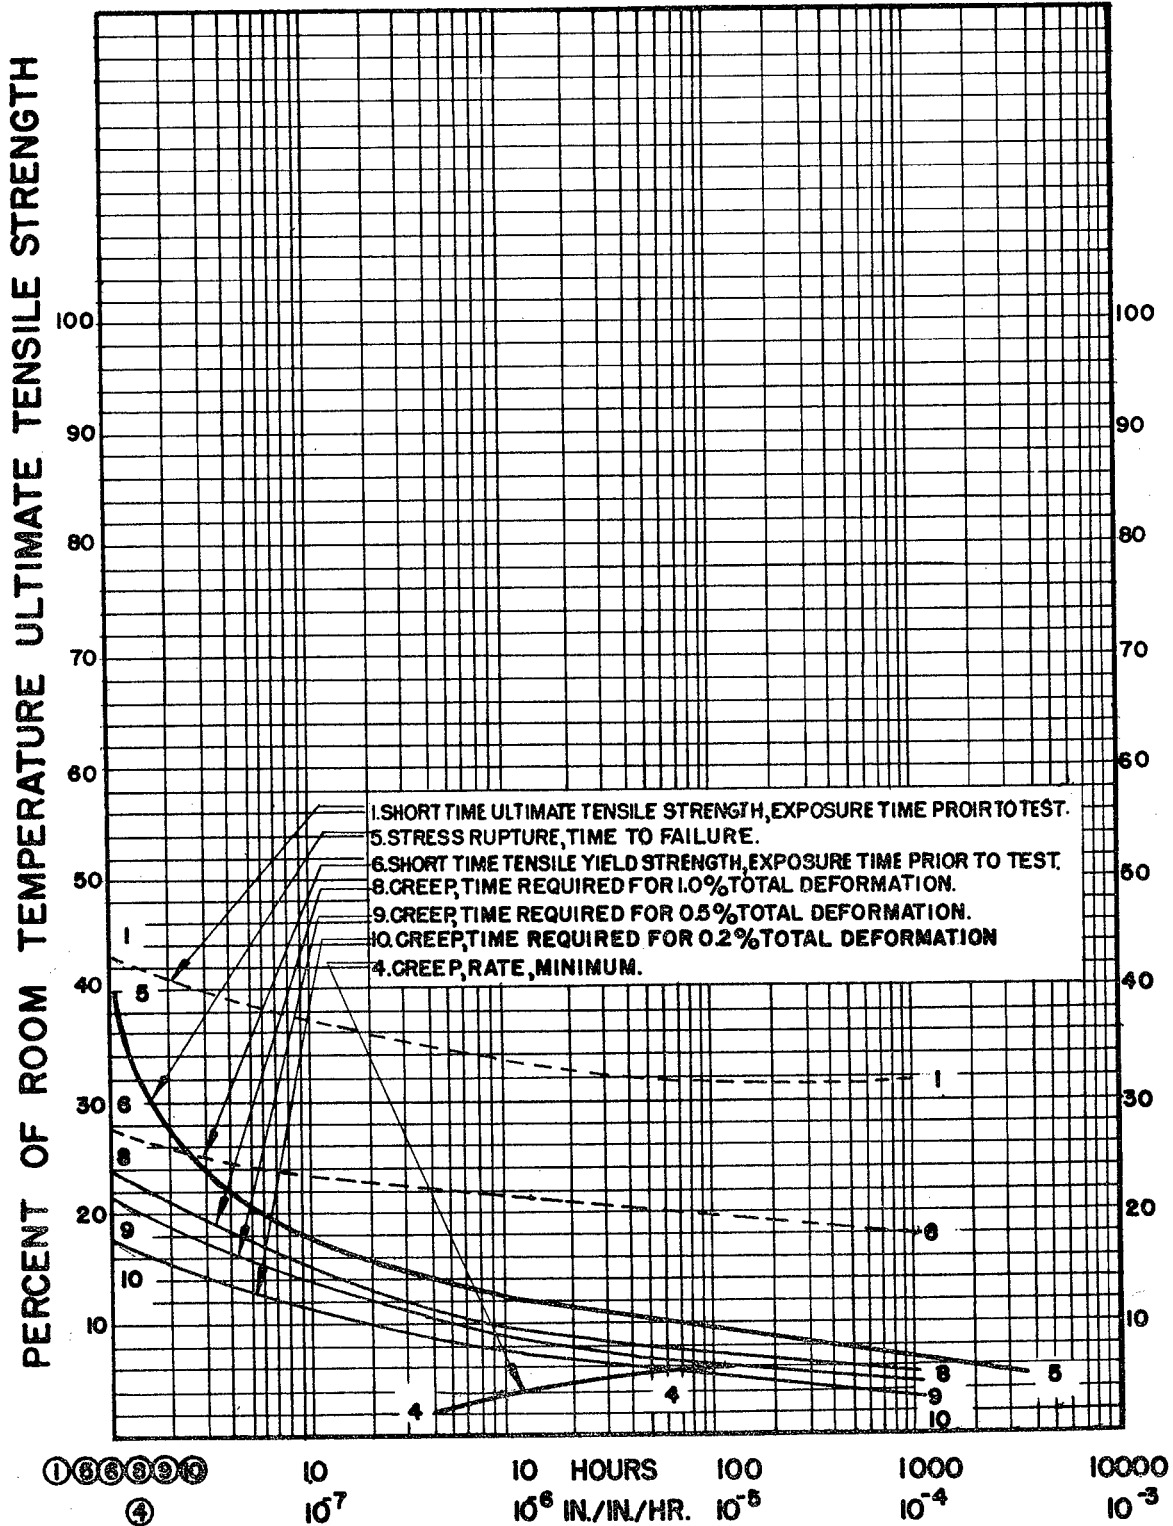


Figure 4.1221 (j). Elevated temperature properties of EM 51-HTA magnesium alloy at 600° F. (tensile). (R. T.  $F_{tu}$  = 37,000 p. s. i.).

PERCENT OF ROOM TEMPERATURE ULTIMATE TENSILE STRENGTH

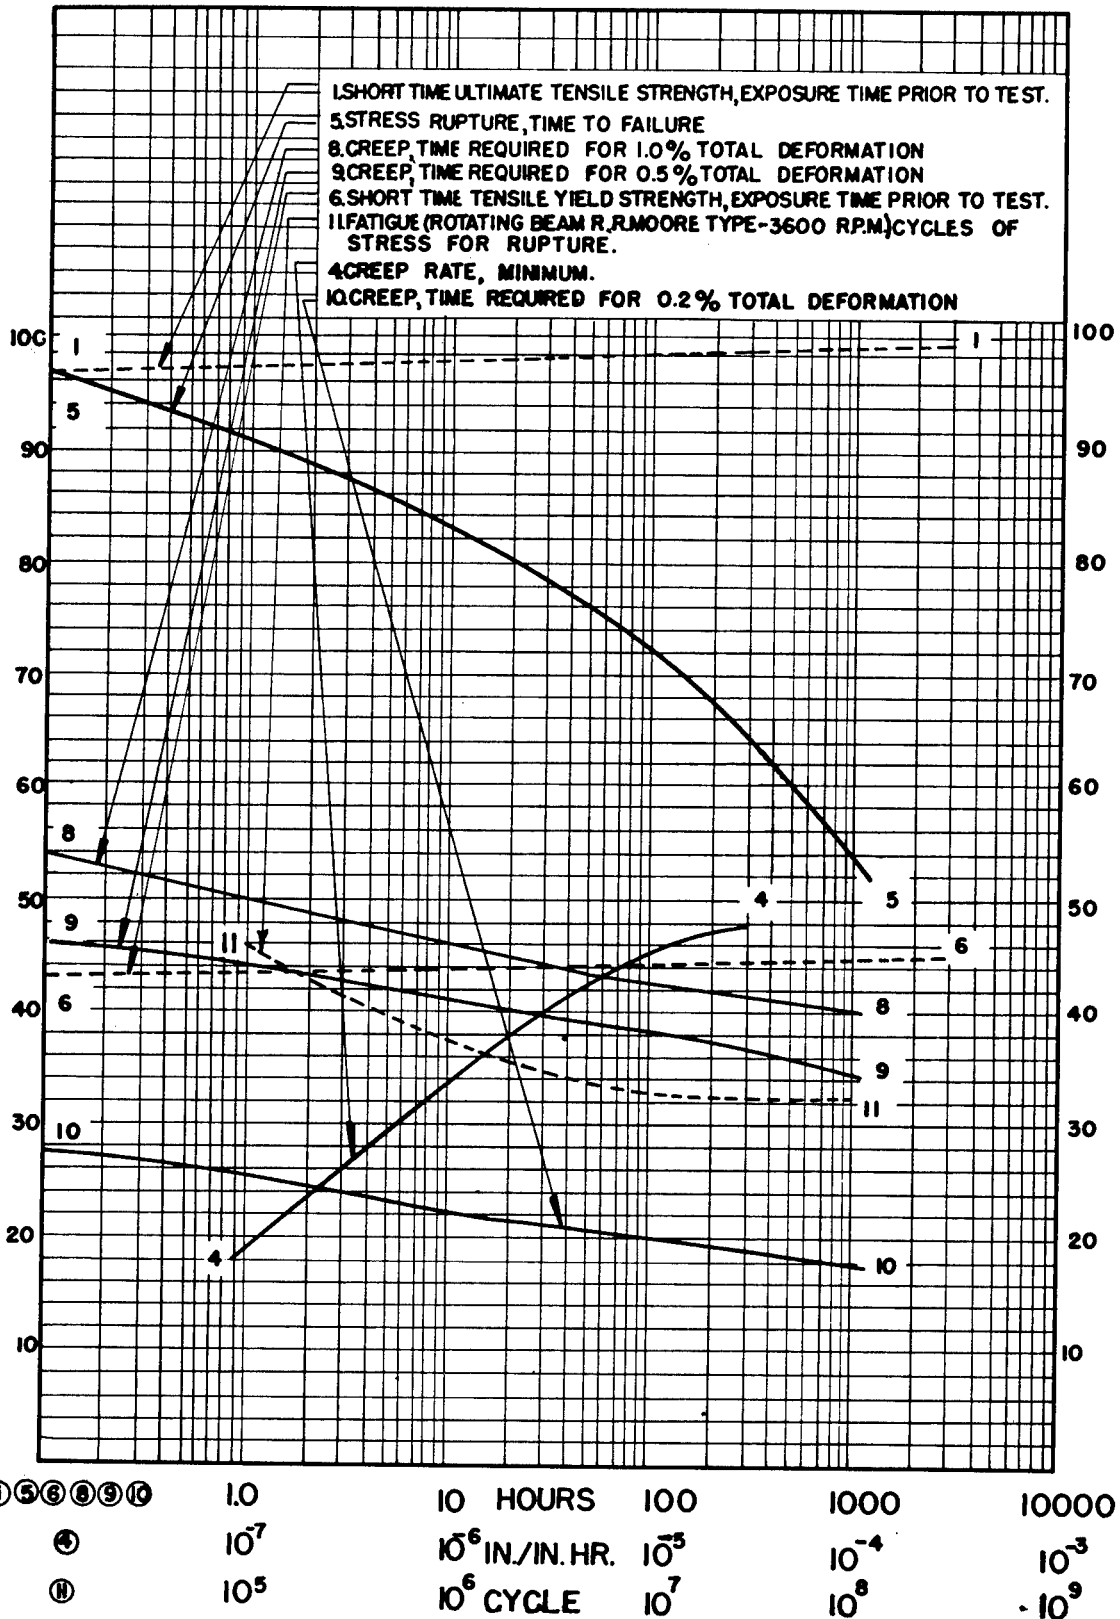


Figure 4.1221 (k). Elevated temperature properties of sand cast dowmetal H or mazlo AM 265 magnesium alloy (heat-treated and stabilized) at 200° F. (tensile and fatigue).



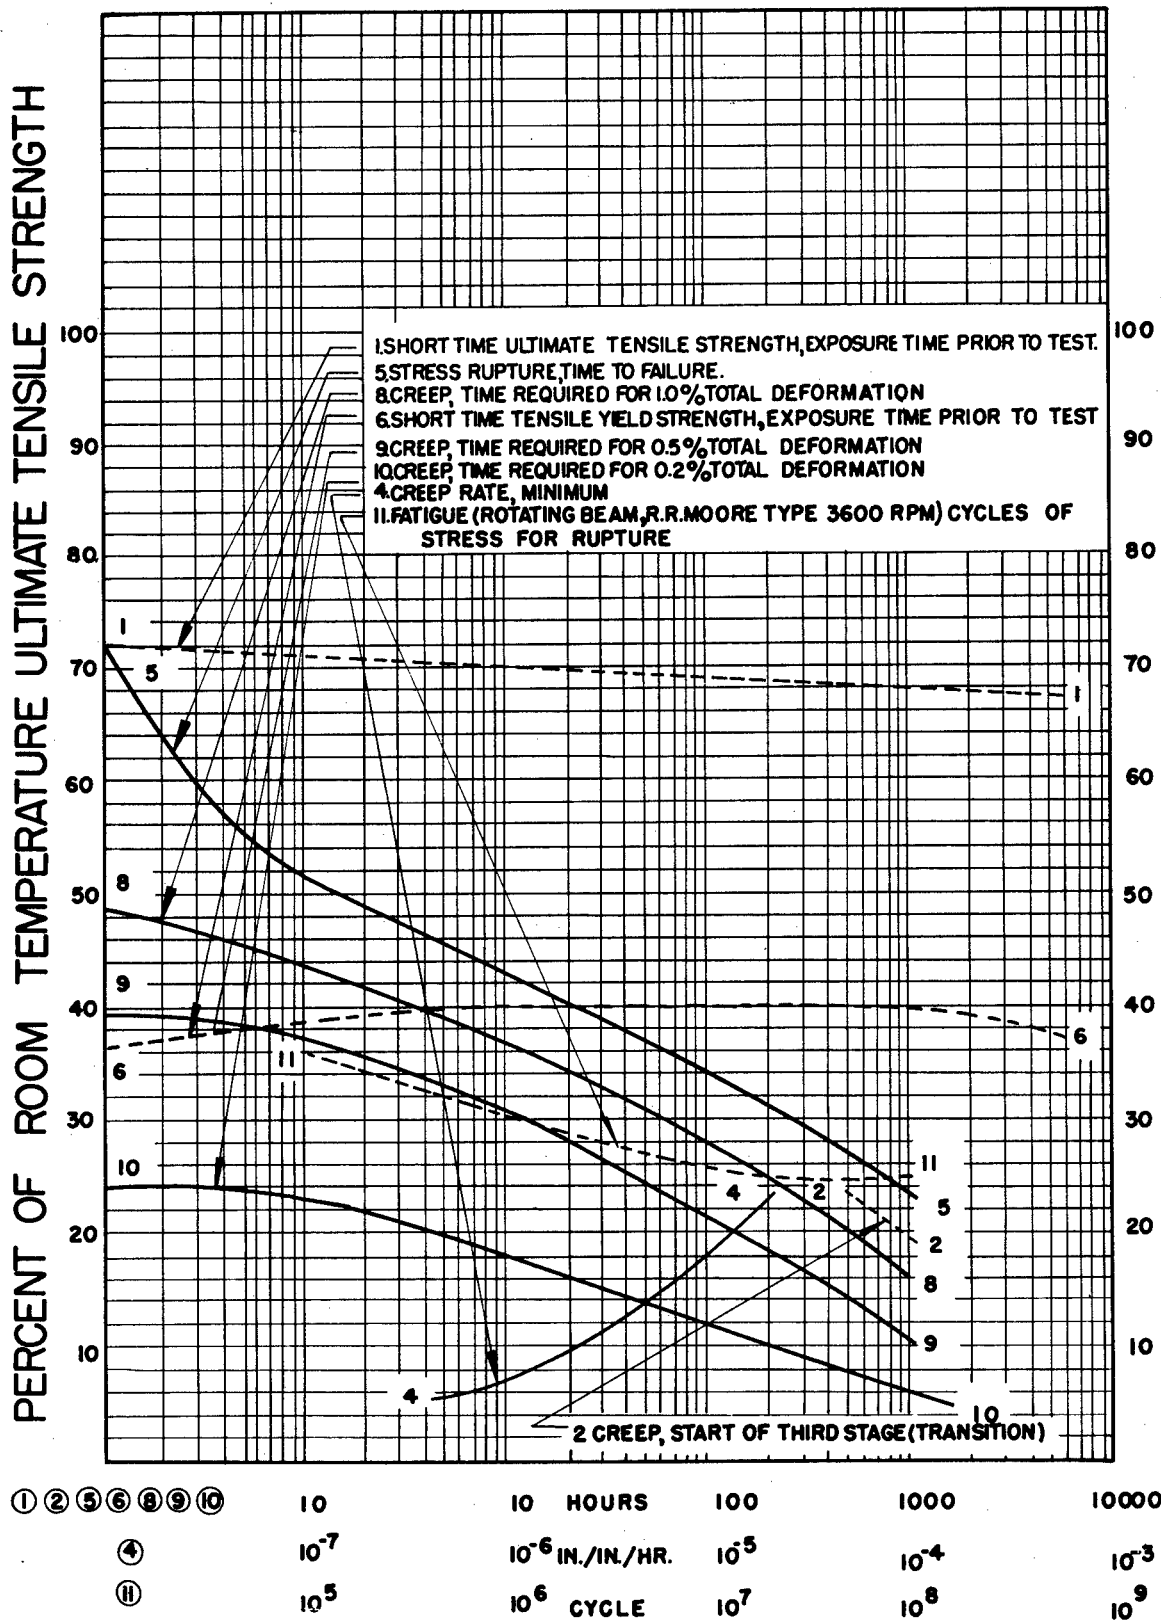


Figure 4.1221 (l). Elevated temperature properties of sand cast downmetal H or mazlo AM 265 magnesium alloy (heat-treated and stabilized) at 300° F. (tensile and fatigue).

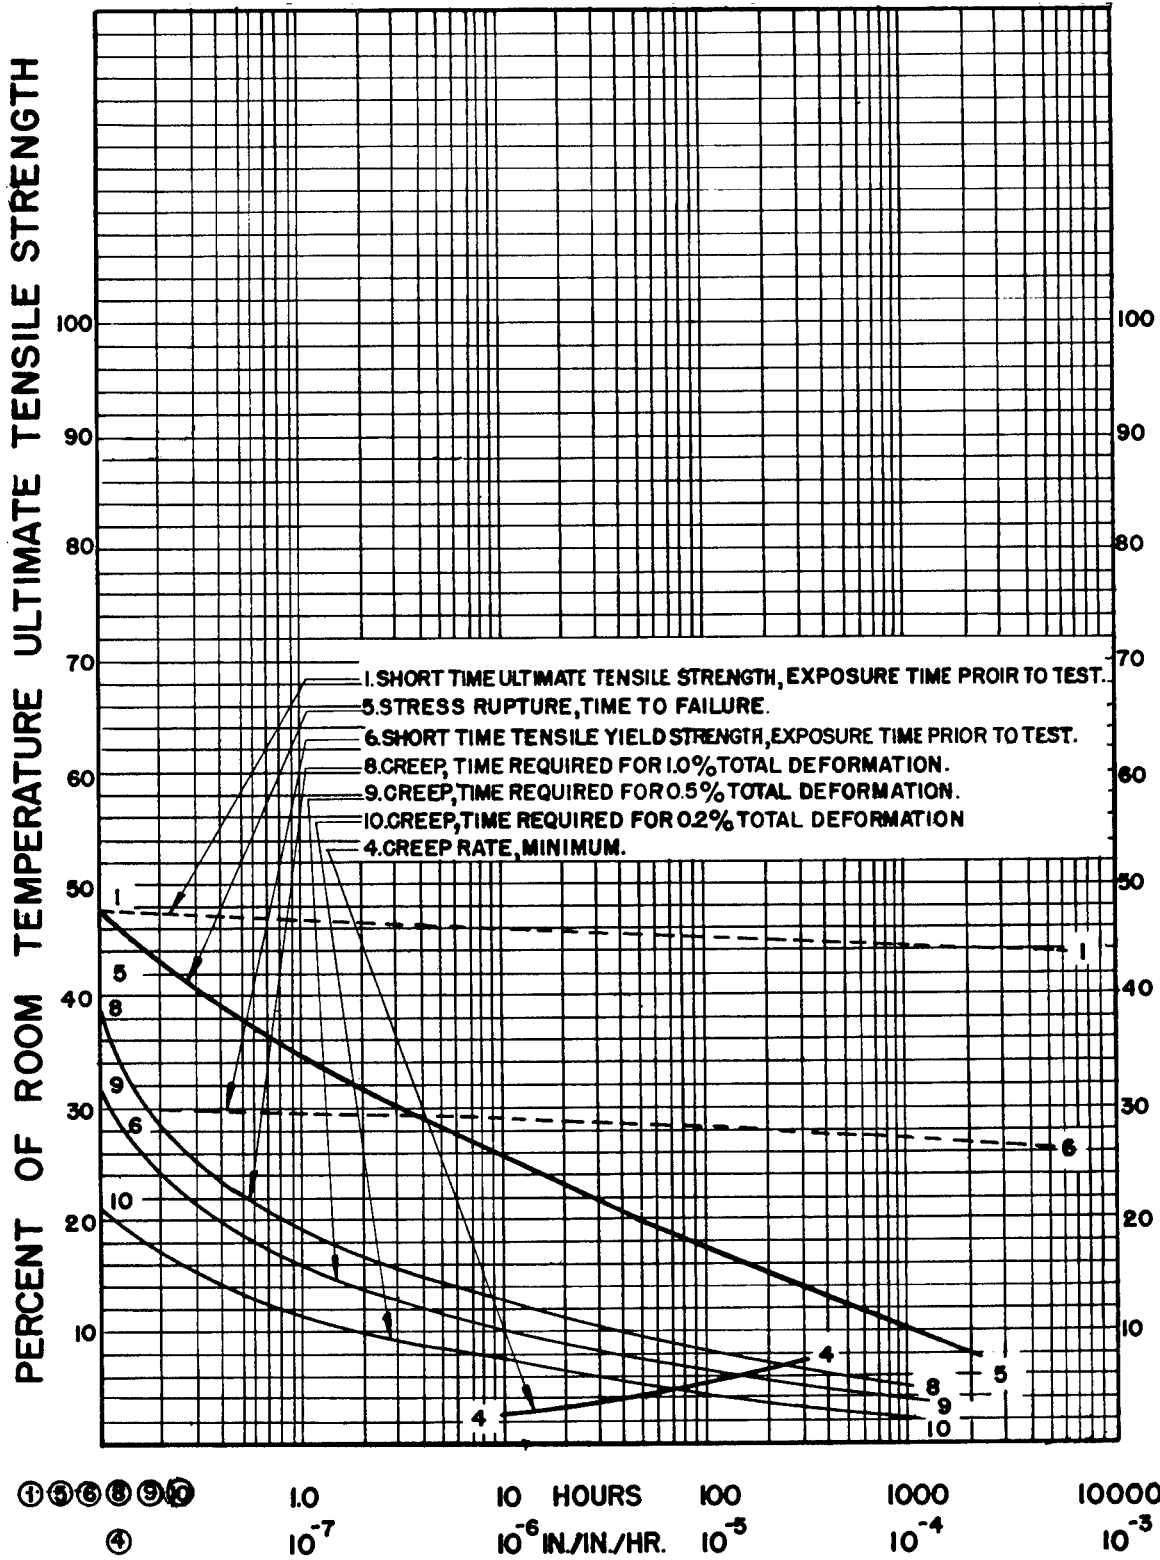


Figure 4.1221 (m). Elevated temperature properties of sand cast downmetal H or mazlo AM 265 magnesium alloy (heat-treated and stabilized) at 400° F. (tensile).

4.1222 *Fatigue properties.* Curves for computing approximate elevated temperature fatigue strengths for O-1HTA, AMC58S-T51, H, and AMC-265 magnesium alloy materials subjected to reversed rotating cantilever bending are shown in figures 4.1221 to 4.1221 (e), 4.1221 (k) and 4.1221 (l). For situations involving fatigue stresses in which the mean stresses are other than zero, consideration must be given to creep-rupture properties in addition to fatigue properties. The effect of variation in frequency of stress application should also be considered.

4.1223 *Creep and stress rupture properties.* Curves for computing the approximate reduction in ultimate tensile strength under long time loads, and for predicting corresponding deformation, for M, O-1HTA, AMC58S-T51, H, AMC-265 and EM51-HTA magnesium alloys are given in figures 4.1221 (a) to 4.1221 (m). Although no actual data are available on shear, bearing, and compression creep properties at elevated temperatures, general reasoning and known room temperature relations indicate that the data may be used to determine approximate shear, bearing, and compressive properties at elevated temperatures as follows:

(a) The percentages of the ultimate tensile strength and the rupture times can be applied directly to shear and bearing ultimate strengths.

(b) The various percentages of total deformation or minimum creep rates are not directly applicable to shear and bearing but may serve as guides. The tensile values may be used for compression where deformations are not excessive.

(c) The percentages of ultimate tensile strength for determining transition times in tension may be used as guides for estimating transition times in shear and bearing.

4.13 CRITERIA FOR DESIGN MECHANICAL PROPERTIES. The test methods used to establish the design mechanical properties appearing in this chapter are discussed below, unless discussed in a note accompanying the table in which the allowables appear.

4.131 *Shear strengths.* The values of shear strengths of magnesium alloy sheet were determined by measuring the load required to punch

from the sheet a 2¼-inch diameter disk, using a special punch and die. The values for other magnesium products were determined from double shear tests of cylindrical specimens in which a 1-inch length is sheared from the center of a specimen 3 inches long. In both cases, the shearing was done with hardened steel tools which have sharp smoothly finished cutting edges that are maintained in that condition.

4.132 *Tensile strengths.* The values of tensile strength of magnesium alloy materials were determined by the methods outlined in reference 1.441.

4.133 *Bearing strengths.* The values of bearing strength of magnesium alloy materials were determined by loading a steel pin inserted in a close fitting hole in material test specimens having widths at least four times the pin diameter and thicknesses not less than one-fourth the pin diameter. Tests were made for edge distances, the distance from the edge of the specimen to the center of the hole in the direction of loading, of 1.5 and 2 times the pin diameter. The bearing yield-strength values were obtained from bearing stress versus hole elongation curves using an offset from the initial straight line portion of the curves of 2 percent of the pin diameter.

## 4.2 Columns

4.21 PRIMARY FAILURE The general formulas for primary instability are given in section 1.38. Formulas applicable to magnesium alloy columns are given in tables 4.21 (a) and (b).

Table 4.21(a). Column Formulas for Magnesium Alloy Extruded Open Shapes

$$\text{General Formula } P/A = \frac{K(F_{cy})^n}{(L/\rho)^m} \text{ (Stress Values are in ksi)}$$

Alloy	K	n	m	Max. P/A
M, AM3S	180	½	1	0.90 $F_{cy}$
FS-1, J-1, O-1, AMC52S, AMC57S.	2,900	¼	1.5	$F_{cy}$
O-1HTA, AMC58S-T5.	3,300	¼	1.5	0.96 $F_{cy}$

Formulas given above are for members that do not fail by local buckling. Reference fig. 4.23 (a).

$F_c$  - COLUMN STRESS IN THOUSANDS OF PSI

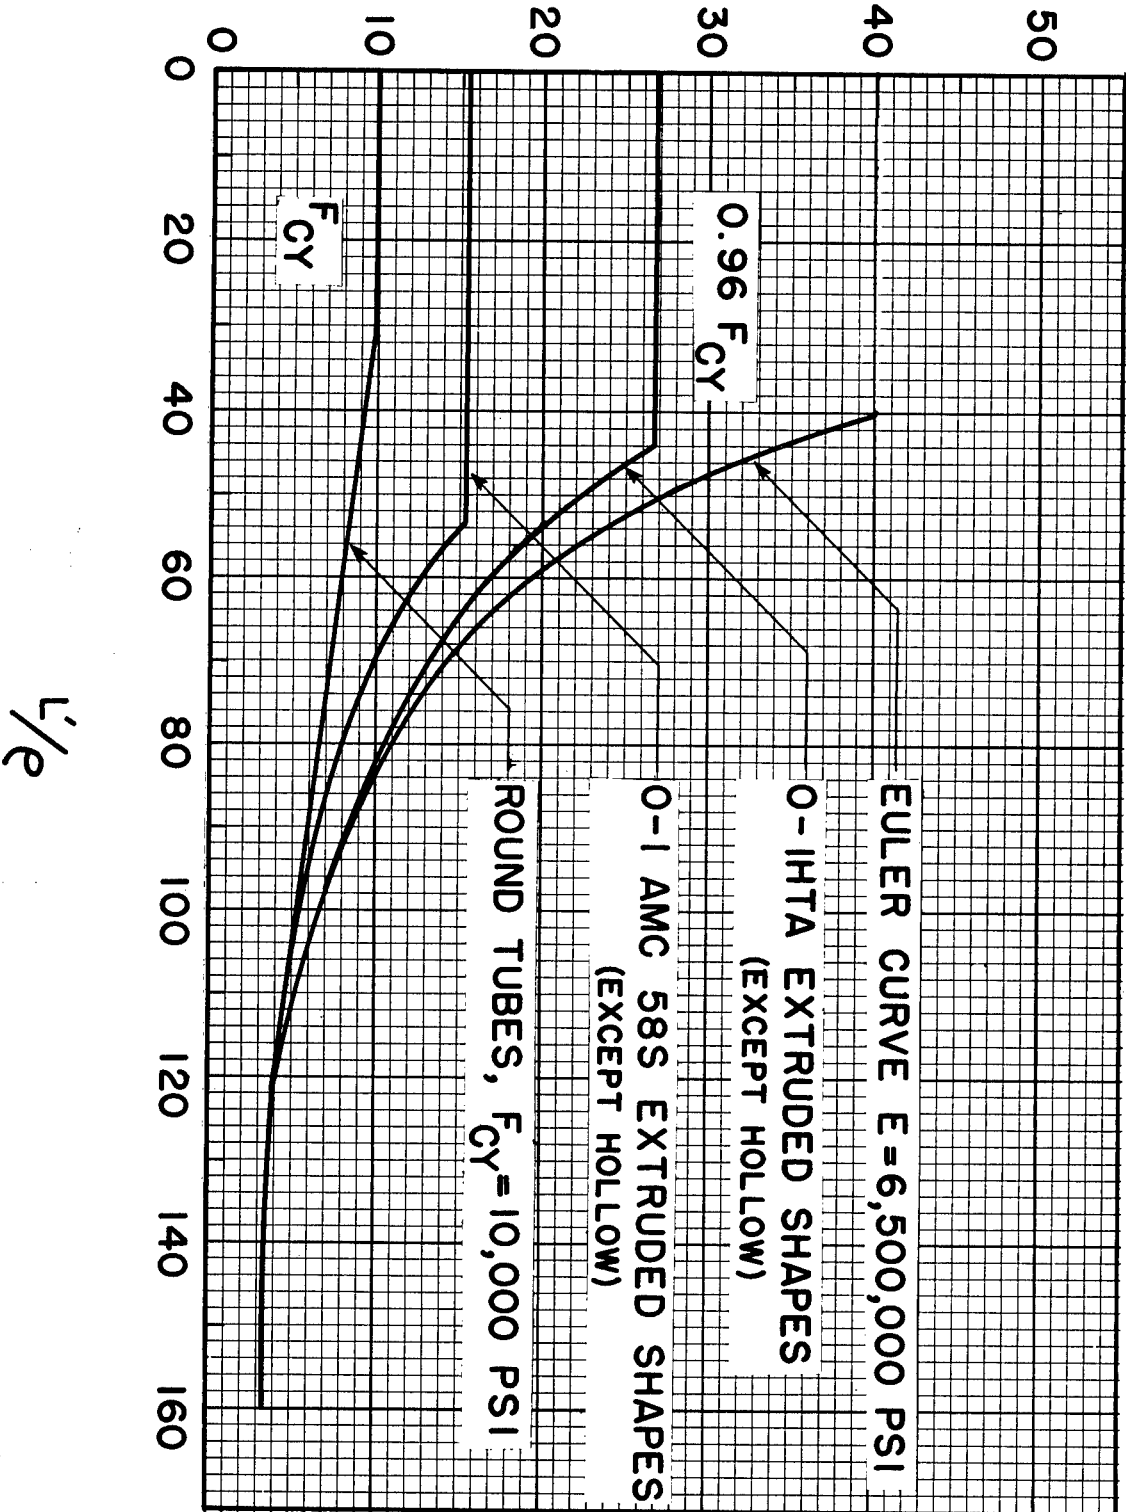


Figure 4.23 (a). Allowable column stresses for magnesium alloy columns.

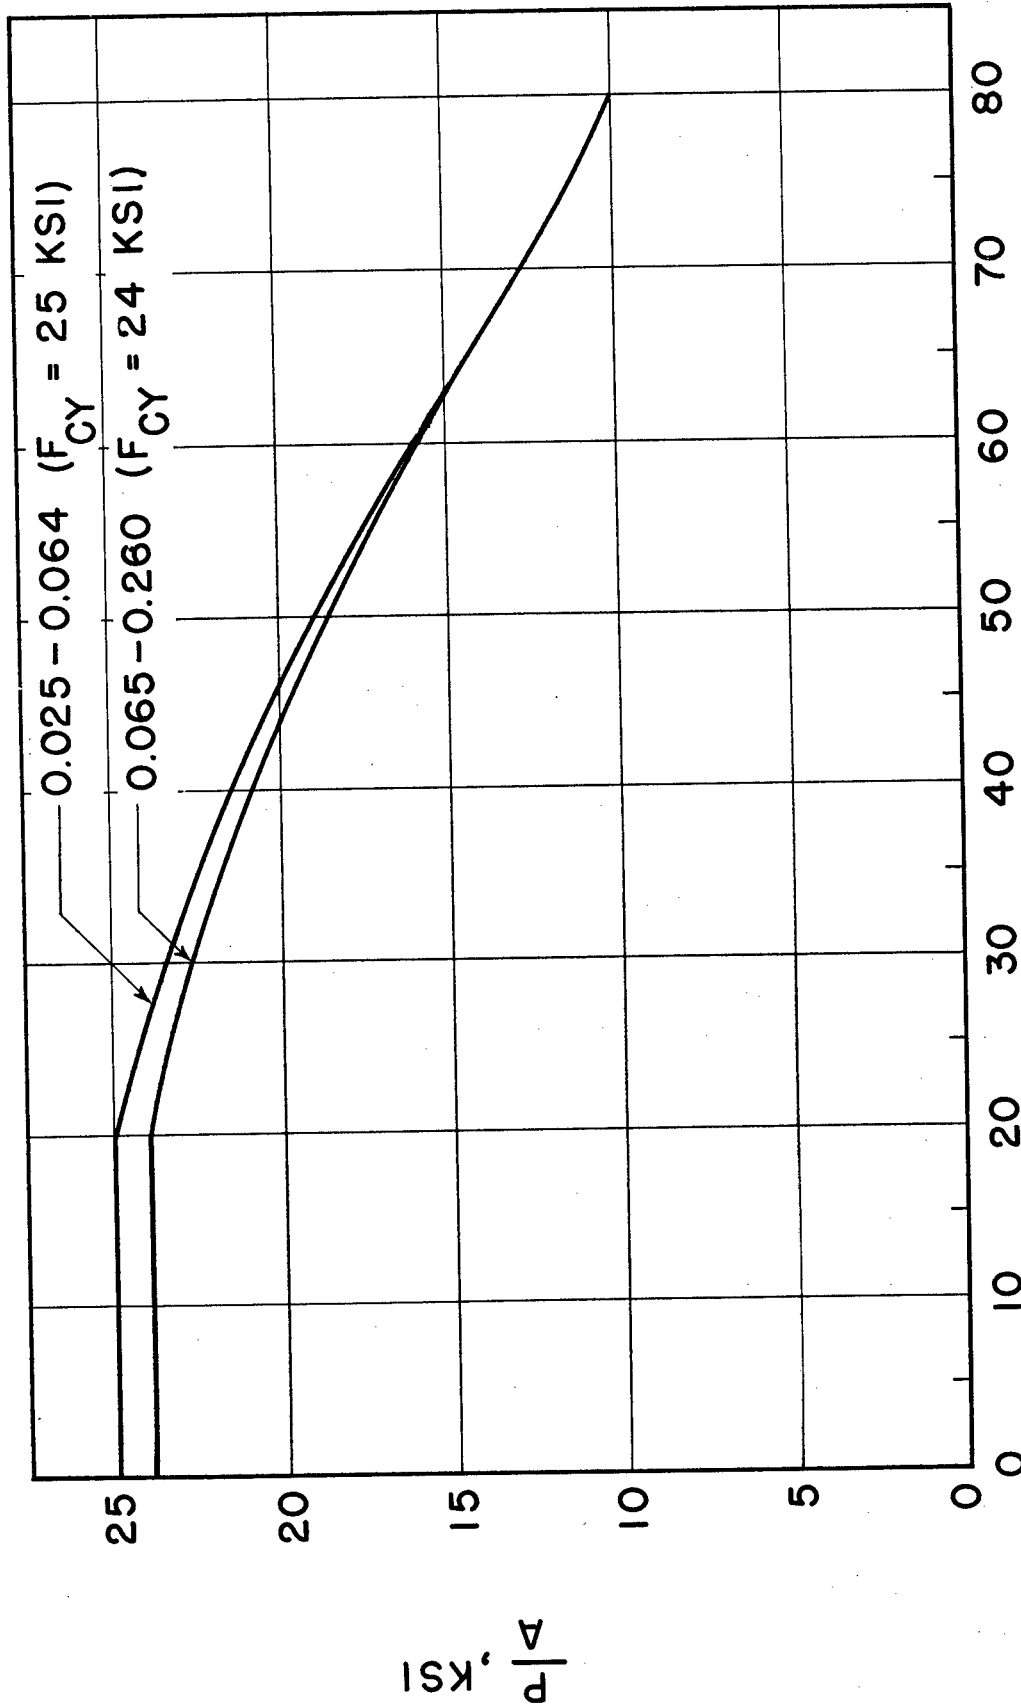


Figure 4.23 (b). Allowable column stresses for FS-1h magnesium alloy sheet.

Table 4.21 (b). Column Formula for FS-1h Magnesium Alloy Sheet

$$\frac{P}{A} = 1.05 F_{cy} - \frac{(1.05 F_{cy})^2 (L/\rho)^2}{4\pi^2 E}$$

Max.  $\frac{P}{A} = F_{cy} = 24 \text{ ksi}$

Reference Fig. 4.23(b)

#### 4.22 LOCAL FAILURE

4.23 COLUMN STRESS CURVES. Curves of the allowable column stresses for various magnesium alloy columns are given in figure 4.23. The allowable stress is plotted against the effective slenderness ratio defined by equation 3.231.

### 4.3 Beams

4.31. GENERAL. See equation 1.323; section 1.525; and reference 1.71 for general information on stress analysis of beams.

#### 4.32 SIMPLE BEAMS

4.321 Round tubes. For round tubes the value of  $F_b$  will depend on the  $D/t$  ratio as well as the compressive yield stress. The bending modulus of rupture of magnesium alloy round tubes is given in figure 4.321. It should be noted that these values apply only when the tubes are restrained against local buckling at the loading points.

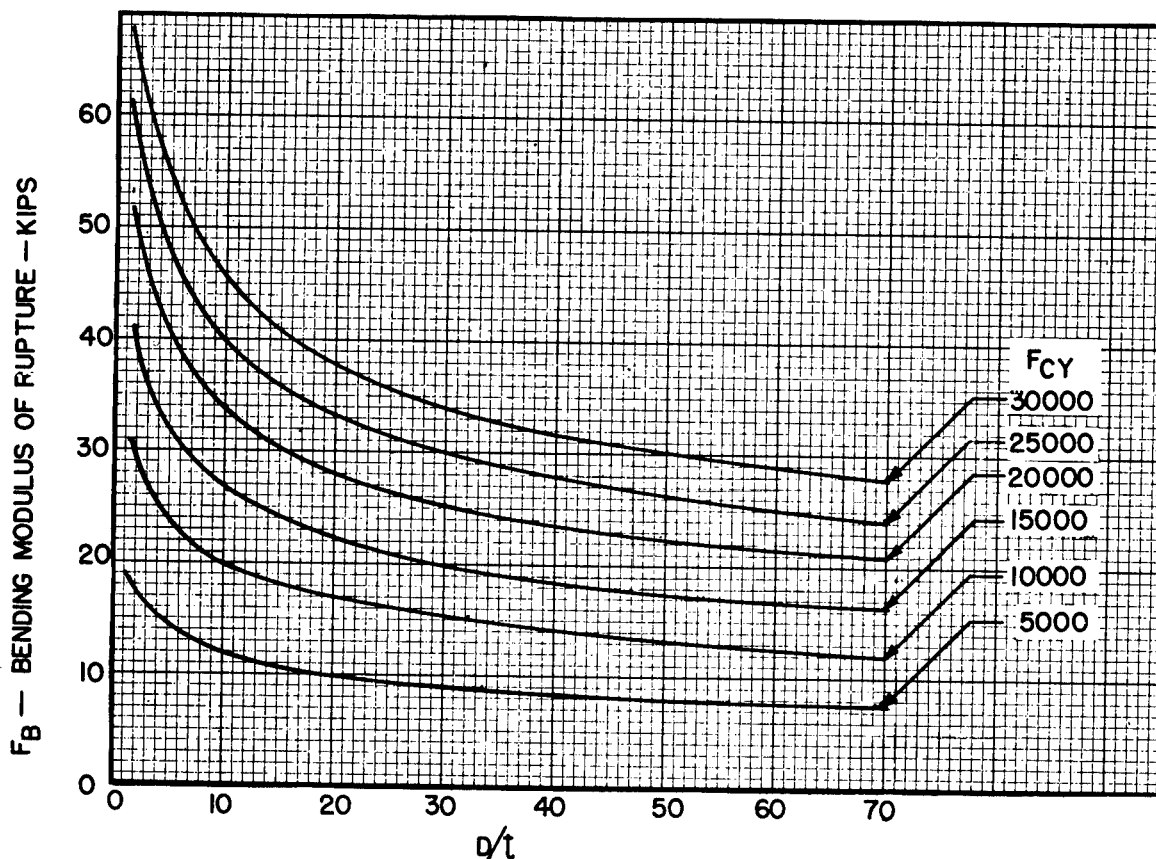


Figure 4.321. Bending modulus of rupture of magnesium alloy round tubing.

Note.—The data for figure 4.321 are for tubes fabricated from magnesium sheet.

#### 4.4 Torsion

4.41 GENERAL. The general statements relating to aluminum alloy tubing, section 3.4, are applicable to magnesium tubing.

4.42 ALLOWABLE TORSION SHEAR STRESSES. An empirical curve of the allowable torsional modulus of rupture for magnesium alloy round tubing (Specification AN-T-71) is given in figure 4.42.

#### 4.5 Combined loadings

#### 4.6 Joints, fittings, and parts

##### 4.61 JOINTS

##### 4.611 Riveted and bolted joints

4.6111 Protruding head rivets. The loads per rivet at which the shear or bearing type of failure occurs are separately calculated and the lower of the two governs the design. The basic shear strengths for protruding head aluminum alloy

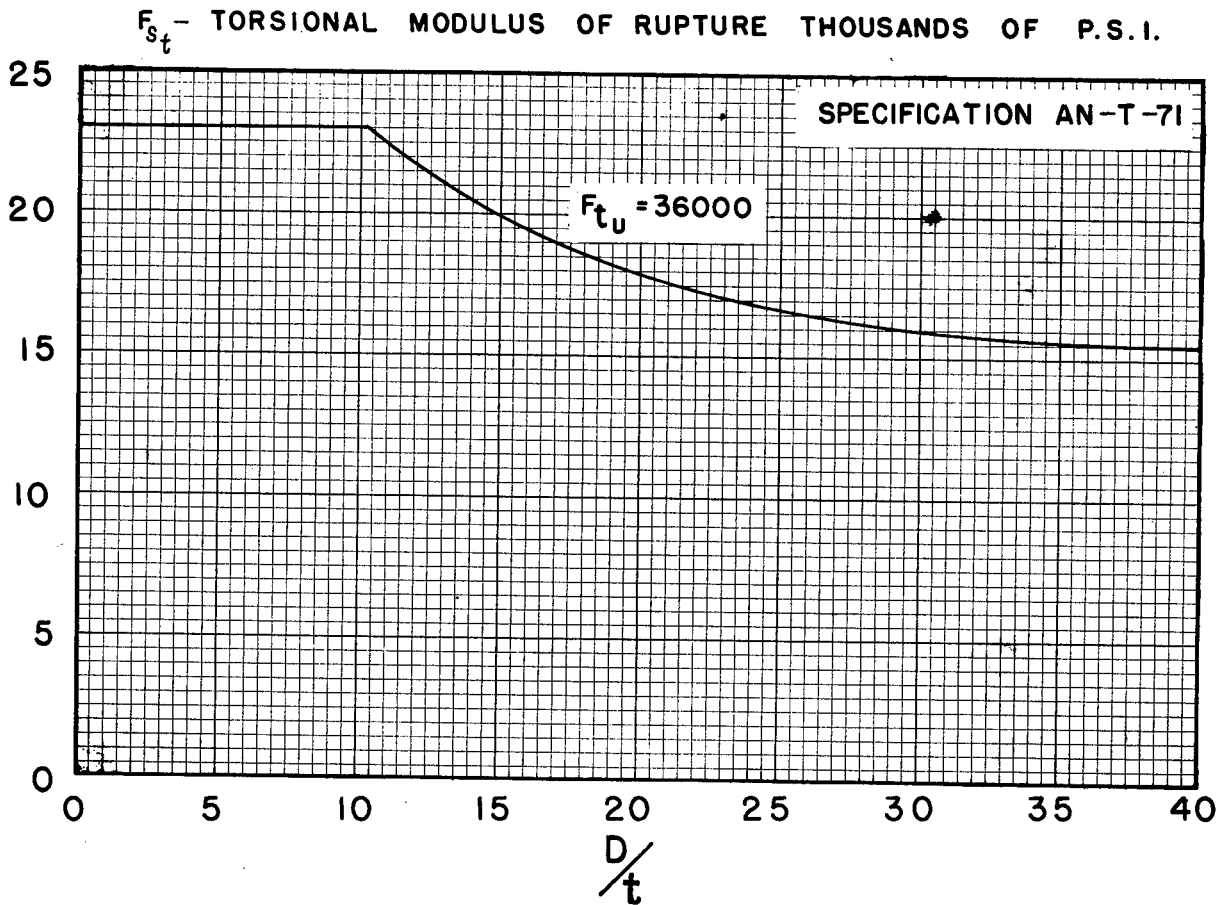


Figure 4.42. Torsional modulus of rupture for magnesium alloy round tubing.

rivets are given in tables 3.6111 (a) and 3.6113 (a). (For magnesium alloy riveting it is unnecessary to use the correction factors of table 3.6111 (a) which account for high bearing stresses on the rivet.) The design bearing stresses for magnesium alloys given in tables 4.111 are applicable to riveted joints (or bolted joints) wherein circular holes are used and where  $D/t < 5.5$ ; where  $D/t > 5.5$ , tests to substantiate yield and ultimate bearing strengths must be made. (A determination as to whether or not yield strength in bearing is more critical than ultimate strength may be necessary for  $D/t < 5.5$ .)

4.6112 *Flush rivets.* Information on this subject is to be supplied at a later date.

4.6113 *Blind rivets.* Table 4.6113 contains ultimate and yield allowable single shear strengths for protruding-head and flush-head blind, 56S aluminum rivets in magnesium alloy sheet. These strengths are applicable only when the grip lengths and rivet hole tolerances are as recommended by the rivet manufacturer.

The strength values were established from test data obtained from tests of specimens having edge distances  $e/D$  equal to or greater than 2.0. Where  $e/D$  values less than 2.0 are used, tests to substantiate yield and ultimate strengths must be made. Ultimate strength values of protruding and flush blind rivets were obtained from the average failing load of test specimens divided by 1.15. Yield strength values were obtained from average yield load test data wherein the yield load is defined as the load at which the following permanent set across the joint is developed:

(a) 0.005 inch up to and including  $\frac{3}{16}$  inch diameter rivets.

(b) 2.5 percent of the rivet diameter for rivet sizes larger than  $\frac{3}{16}$  inch diameter.

Blind rivets should not be used in applications where appreciable tensile loads on the rivets will exist. Reference should be made to the requirements of the applicable procuring or certifying agency relative to the use of blind rivets.



Table 4.6113. Ultimate and Yield Strengths for Blind 56S Aluminum Cherry Rivets in Magnesium Sheet (Pounds)

## ULTIMATE STRENGTHS

Installation .....	Protruding head			100° double dimpled <sup>a b</sup>			100° machine countersunk <sup>c</sup>		
Rivet type .....	CR 157 <sup>d</sup>			CR 156 <sup>d</sup>					
Sheet material .....	FS-1h								
$t^e$ \ D	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$	$\frac{1}{8}$	$\frac{5}{32}$	$\frac{3}{16}$
0.020 .....				95					
0.025 .....	200	214		140	240				
0.032 .....	244	320	338	200	270	330			
0.040 .....	290	360	430	225	300	370	200		
0.051 .....	345	424	526	260	340	430	260	320	
0.064 .....	390	490	620		390	495	305	380	*510
0.072 .....	395	530	680			515	340	410	520
0.081 .....		580	750			535	370	450	540
0.091 .....		605	825					495	590
0.102 .....			875					550	660
0.125 .....								570	820

## YIELD STRENGTHS

0.020 .....				73					
0.025 .....	177	214		112	190				
0.032 .....	220	295	320	182	253	288			
0.040 .....	275	360	415	190	259	288	190		
0.051 .....	334	424	510	260	267	356	230	241	
0.064 .....	365	490	600		356	450	288	345	310
0.072 .....	380	530	640			483	316	386	374
0.081 .....		560	690			512	357	426	443
0.091 .....		580	730					472	495
0.102 .....			765					530	563
0.125 .....								565	690

<sup>a</sup> The double-dimpled allowables also apply to dimpled-machine countersunk joints. In this case the allowable is determined by the gage of the upper dimpled sheet. The gage of the lower machine countersunk sheet must be at least  $2\frac{1}{2}$  times the height of the preformed rivet head.

<sup>b</sup> In dimpled installations allowables shall not be obtained by extrapolation for skin gages other than those shown.

<sup>c</sup> In the case of machine countersunk joints where the lower sheet is thinner than the upper, the bearing allowable for the lower sheet-rivet combination should be computed.

<sup>d</sup> See table 3.6112 (a) for rivet shear strengths.

<sup>e</sup> Sheet gage is that of the thinnest sheet for protruding head and double-dimpled installations. For machine countersunk installations sheet gage is that of the upper sheet.

Yield values of the sheet-rivet combinations marked thus (\*) are less than  $\frac{2}{3}$  of the indicated ultimate values.

Other sheet-rivet combinations may be used subject to specific approval of the procuring or certifying agency.

4.612 *Welded joints*

4.6121 *Fusion welds*


4.6122 *Spot welding.* The permissibility of the use of spot welding on structural parts is governed by the requirements of the procuring or certifying agency. Design shear strength allowables for spotwelds in various magnesium alloys are given in table 4.6122 (a); the thickness ratio of the thickest sheet to the thinnest outer sheet in the combination should not exceed 3:1. Table 4.6122 (b) gives the minimum allowable edge distance for spotwelds in magnesium alloys; these values may be reduced for nonstructural applications, or for applications not depended upon to develop the full tabulated weld strength.

Table 4.6122 (a). *Spotweld Maximum Design Shear Strength Standards for Magnesium Alloys*<sup>1</sup>

Nominal thickness of thinner sheet (inch)	Magnesium alloys		Nominal thickness of thinner sheet (inch)	Magnesium alloys	
	QQ-M-54	QQ-M-44		QQ-M-54	QQ-M-44
	Pounds	Pounds		Pounds	Pounds
0.020	51	69	0.072	279	378
0.025	71	97	0.081	320	434
0.032	102	139	0.091	368	498
0.040	137	185	0.102	433	586
0.051	186	251	0.114	488	658
0.064	242	328	0.125	544	735

<sup>1</sup> *Magnesium Alloys.* Magnesium alloys, conforming to Specifications QQ-M-44 and QQ-M-54, may be spotwelded in any combination.

Table 4.6122 (b). *Minimum Edge Distances for Spot-Welded Joints*

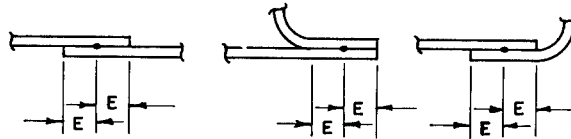

Thickness thinner sheet (inch)	Edge distance (E)	Thickness thinner sheet (inch)	Edge distance (E)
0.016	$\frac{3}{16}$	0.060	$\frac{11}{32}$
0.020	$\frac{3}{16}$	0.070	$\frac{3}{8}$
0.025	$\frac{7}{32}$	0.080	$\frac{13}{32}$
0.030	$\frac{1}{4}$	0.090	$\frac{7}{16}$
0.035	$\frac{1}{4}$	0.100	$\frac{7}{16}$
0.040	$\frac{9}{32}$	0.120	$\frac{1}{2}$
0.045	$\frac{5}{16}$	0.125	$\frac{9}{16}$
0.050	$\frac{5}{16}$	0.157	$\frac{5}{8}$

Intermediate gages will conform to the requirement for the next thinner gage shown.

For edge distances less than those specified above, appropriate reductions in the spotweld allowable loads shall be made. These reductions shall be subject to approval by the procuring or certifying agency.

Where alloys listed in table 4.6122 (a) are spot-welded in combination the lower spotweld strength shall be used.

4.613 *Adhesive bonded joints.* Joints may in some instances be made to advantage by the use of an adhesive suitable for the structural bonding of metals. This subject is discussed in reference 2.614.

## CHAPTER 5

### MISCELLANEOUS METALS

#### 5.1 General Properties

##### 5.11 NORMAL (ROOM) TEMPERATURE PROPERTIES

5.111 *Design mechanical properties.* The general strength properties and related characteristics of various metals and alloys at normal (room) temperatures are listed in the table 5.111:

Table 5.111. *Design Mechanical Properties—Castings*  
(Kips Per Square Inch)

Type.....	Castings			
	Aluminum bronze	Manganese bronze	Hydraulic bronze	Phosphor bronze
Alloy.....				
Specification.....	QQ-B-671	QQ-B-726	QQ-B-691 (composition 2)	QQ-B-691 (composition 6)
Condition.....	As cast			
$F_{tu}^a$ .....	65	65	30	35
$F_{tv}$ .....	28	25	-----	-----
$F_{cu}$ .....	-----	-----	-----	-----
$F_{su}$ .....	40	40	-----	-----
$F_{bru}(e/D=1.5)$ .....	-----	-----	-----	-----
$F_{bru}(e/D=2.0)$ .....	80	80	-----	-----
$F_{bru}(e/D=1.5)$ .....	-----	-----	-----	-----
$F_{bru}(e/D=2.0)$ .....	-----	-----	-----	-----
Percent elongation.....	22	20	20	18
$E, E_c$ .....	14, 000	14, 000	-----	-----
$G$ .....	4, 500	4, 500	-----	-----

<sup>a</sup> Standard structural symbols are explained in sec. 1.2, ch. 1.

The above values are minimum values obtained from cast test bar specimens. Reference should be made to the specific requirements of the procuring or certifying agency with regard to the use of the above values in the design of castings.