

NOT MEASUREMENT SENSITIVE
------------------------------

MIL-PRF-81309G  
15 July 2014  
SUPERSEDING  
MIL-PRF-81309F  
16 May 2005

## PERFORMANCE SPECIFICATION

### CORROSION PREVENTIVE COMPOUNDS, WATER DISPLACING, ULTRA-THIN FILM

This specification is approved for use by all Departments and Agencies of the Department of Defense.

#### 1. SCOPE

1.1 Scope. This specification covers the requirements for three types and two classes containing two grades of propellants of ultra-thin film, water displacing, corrosion preventive compounds which may be applied by dipping, spraying, brushing or by spraying from self-pressurized containers (see 6.1).

1.2 Classification. The compounds are of the following types, classes, and propellant grades as specified (see 6.2b).

1.2.1 Types. The types of compounds are as follows:

Type I - Soft Film (with mildew inhibitor).

Type II - Soft film (general purpose grade).

Type III - Soft film (avionic grade).

1.2.2 Classes. The classes are as follows:

Class 1 - Bulk container (brush, dip or spray application).

Class 2 - Self-pressurized container (for spray application).

Comments, suggestions, or questions on this document should be addressed to: Commander, Naval Air Warfare Center Aircraft Division, Code 4L8000B120-3, Highway 547, Lakehurst, NJ, 08733-5100 or emailed to <a href="mailto:michael.sikora@navy.mil">michael.sikora@navy.mil</a> . Since contact information can change you may want to verify the currency of this address information using the ASSIST Online database at <a href="https://assist.dla.mil">https://assist.dla.mil</a> .
---


## MIL-PRF-81309G

1.2.3 Grades. The grades are as follows:

a - Grade 134a - Hydrofluorocarbon (HFC) propellant.

b - Grade CO<sub>2</sub> - Carbon dioxide (CO<sub>2</sub>) propellant.

1.3 Part or identifying number (PIN). PINs to be used for compounds acquired to this specification are created as follows:

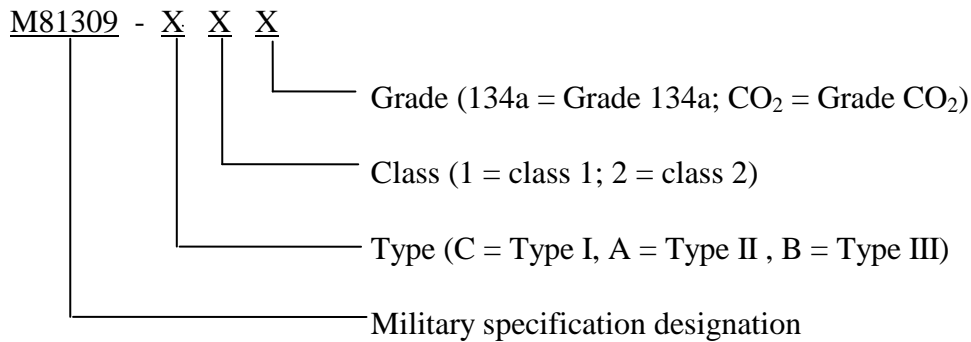

Example: A type II, class 2, Grade CO<sub>2</sub> compound will be designated as follows:  
M81309-A2CO<sub>2</sub>

## 2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

## FEDERAL SPECIFICATIONS

CCC-C-46	-	Cloth, Cleaning, Nonwoven Fabric (Inactive for New Design)
PPP-C-96	-	Cans, Metal, 28 Gage and Lighter

## MIL-PRF-81309G

## DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-680	-	Degreasing Solvent
MIL-PRF-5425	-	Plastic Sheet, Acrylic, Heat Resistant
MIL-DTL-5541	-	Chemical Conversion Coatings on Aluminum and Aluminum Alloys
MIL-DTL-18001	-	Anode, Sacrificial Zinc Alloy
MIL-PRF-23377	-	Primer Coatings: Epoxy, High-Solids
MIL-W-81381/11	-	Wire, Electric, Fluorocarbon/polyimide Insulated, Medium Weight, Silver Coated Copper Conductor, 600 Volts, 200 Degrees C, Nominal 8.4 or 15.4 Mil Wall (Inactive for New Design)
MIL-PRF-85285	-	Coating: Polyurethane, Aircraft and Support Equipment
MIL-PRF-85570	-	Cleaning Compounds, Aircraft, Exterior

## DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-290	-	Packaging and Marking of Petroleum and Related Products
MS3112	-	Connectors, Receptacle, Electric, Series 1, Box Mounting Flange, Bayonet Coupling, Solder Contact
MS3116	-	Connectors, Plug, Electric, Series 1, Solder Type, Straight, Bayonet Coupling (Inactive for New Design)

(Copies of these documents are available online at <http://quicksearch.dla.mil/> or <https://assist.dla.mil/>.)

2.2.2 Other Government documents, drawings, and publications. The following Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues are those cited in the solicitation.

## CODE OF FEDERAL REGULATIONS

## ENVIRONMENTAL PROTECTION AGENCY

40 CFR 61	-	National Emission Standards for Hazardous Air Pollutants
40 CFR 82	-	Protection of Stratospheric Ozone

(Copies of these documents are available online at <http://www.gpo.gov/fdsys/>.)

MIL-PRF-81309G

U.S. DEPARTMENT OF HEALTH AND HUMAN SERVICES

National Toxicology Program's Annual Report on Carcinogens

(Copies of this document are available online at  
<http://ehp.niehs.nih.gov/docs/admin/indivrocform.html>.)

2.3 Non-Government publications. The following document forms a part of this document to the extent specified herein. Unless otherwise specified, the issues of this document are those cited in the solicitation or contract.

AMERICAN BEARING MANUFACTURERS ASSOCIATION

AISI C-52100 steel, grade 25 extra polish (EP)

(A copy of this document is available online at <http://www.americanbearings.org>.)

ASTM INTERNATIONAL

ASTM B117	-	Standard Practice for Operating Salt Spray (Fog) Apparatus
ASTM D93	-	Standard Test Methods For Flash Point by Pensky-Martens Closed Cup Tester
ASTM D877	-	Standard Test Method for Dielectric Breakdown Voltage of Insulating Liquids Using Disk Electrodes
ASTM D3065	-	Standard Test Methods for Flammability of Aerosol Products
ASTM F484	-	Standard Test Method for Stress Cracking of Acrylic Plastics in Contact with Liquid or Semi-Liquid Compounds
ASTM F502	-	Standard Test Method for Effects of Cleaning and Chemical Maintenance Materials on Painted Aircraft Surfaces

(Copies of these documents are available online at [www.astm.org](http://www.astm.org).)

## MIL-PRF-81309G

## SAE INTERNATIONAL

SAE AMS5046	-	Carbon Steel, Sheet, Strip, and Plate (SAE 1020 and 1025) Annealed
SAE AS22805	-	Spray Kit, Self Pressurized
SAE AMS-P-83310	-	Plastic Sheet, Polycarbonate, Transparent
SAE AMS-QQ-A-250/4	-	Aluminum Alloy 2024, Plate and Sheet

(Copies of these documents are available online at [www.sae.org](http://www.sae.org).)

2.4 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

### 3. REQUIREMENTS

3.1 Qualification. The compounds furnished under this specification shall be products that are authorized by the qualifying activity for listing on the applicable qualified products list before contract award (see 4.3 and 6.3).

3.2 Materials. The compounds shall be nonvolatile base materials dispersed in a solvent to form a fluid formulation conforming to this specification. Aromatic, chlorinated, chlorofluorocarbon, hydrochlorofluorocarbon solvents, Class I Ozone Depleting Substances (ODSs), Hexavalent Chromium, Asbestos or Polychlorinated Biphenyls (PCB) shall not be used in the formulation. The compounds shall be homogeneous, free of lumps, dirt or other suspended matter, and free of water, chlorides, silicones, and other impurities (see 6.5).

3.2.1 Composition. The composition of the compounds shall be optional with the manufacturer, but shall be within the limitations specified herein (see 3.2, 3.3, 3.4 and 3.5). Self-pressurized containers may use the following propellants or may request approval for an alternative from the qualifying activity.

3.2.1.1 Grade 134a propellant. The propellant for Grade 134a shall consist of hydrofluorocarbons or a blend containing hydrofluorocarbons. Grade 134a propellant blends shall contain no chlorinated solvents, hydrochlorofluorocarbons, or fully halogenated chlorofluorocarbons.

3.2.1.2 Grade CO<sub>2</sub> propellant. The propellant for Grade CO<sub>2</sub> shall consist of carbon dioxide. The propellant shall contain no chlorinated solvents, hydrochlorofluorocarbons, or fully halogenated chlorofluorocarbons.

3.3 Toxicity. The compound shall not adversely affect the health of personnel when used for its intended purpose. The compound shall not contain known or suspected human

## MIL-PRF-81309G

carcinogens, as defined by the National Toxicology Program's Annual Report on Carcinogens. Prior to listing on the Qualified Products List, the manufacturer shall obtain a satisfactory toxicity review from Navy and Marine Corps Public Health Center (NMCPHC) using (see 4.3.1 and 6.4). In addition, an Material Safety Data Sheet (MSDS) for the compound shall be prepared and submitted to the Qualifying Activity.

3.4 Environmental compatibility. The compound shall contain no Class I or II Ozone Depleting Substances as specified in 40 CFR 82. The compound shall contain no Hazardous Air Pollutants (HAPS) as defined in 40 CFR 61.

3.5 Mildew inhibitor additive for Type I. The composition of Type I shall contain 0.5 percent of mildew inhibitor additive (Omacide 100) or equivalent as approved by the qualifying activity (see 6.3.1).

3.6 Performance characteristics. The corrosion preventive compound shall conform to the requirements in Table I when tested in accordance with Table II.

## MIL-PRF-81309G

TABLE I. Performance characteristics.

Property	Requirement	Type I, Class 1	Type I, Class 2	Type II, Class 1	Type II, Class 2	Type III, Class 1	Type III, Class 2
Acid salt fog protection, minimum cycles to unacceptable corrosion <u>1/</u>	2 (carbon steel) 8 (410 stainless steel)	X	X	X	X	X	X
Application	Brush, Dip, or Spray  Sprayable after 20 hours at 40 °F	X	X	X	X	X	X
Compatibility with polyimide, wiring insulation	No cracking or degradation of insulation following prolonged exposure; No dielectric leakage	X	X	X	X	X	X
Dielectric strength	25,000 volts minimum	X	X	X	X	X	X
Effect on acrylic plastic and polycarbonate	No crazing, cracking, or staining	X	X	X	X	X	X
Effect on urethane paint	No crazing, cracking, or staining	X	X	X	X	X	X
Effect on electronic components, maximum change from initial contact resistance	5 milliohms					X	X

## MIL-PRF-81309G

TABLE I. Performance characteristics - Continued.

Property	Requirement	Type I, Class 1	Type I, Class 2	Type II, Class 1	Type II, Class 2	Type III, Class 1	Type III, Class 2
Fill weight, minimum	Grade 134a, oz. Grade CO <sub>2</sub> , oz.		14.5 11.0		14.5 11.0		14.0 11.0
Film appearance	Uniform and light brown or lighter Simulated corrosion spots shall be visible by the unaided eye	X  X	X  X	X  X	X  X	X	X
Film thickness, maximum	0.5 mil 0.2 mil	X	X	X	X	X	X
Flame projection	Propellant shall exhibit no flame extension or flashback		X		X		X
Flash point, minimum	140 °F	X		X		X	
Friction coefficient, maximum	0.20	X	X	X	X	X	X
Functional Penetration	No panel faying surface area to be less than 80 percent wetted in 24 hours. Average of three panels to be 85 percent or better, wetted in 24 hours	X	X	X	X	X	X
Leakage/distortion of cans	None		X		X		X
Neutral salt fog protection, minimum hours to unacceptable corrosion <u>1</u> /	336 hours	X	X	X	X	X	X
Net content	As specified in the contract	X		X		X	



## MIL-PRF-81309G

TABLE I. Performance characteristics - Continued.

Property	Requirement	Type I, Class 1	Type I, Class 2	Type II, Class 1	Type II, Class 2	Type III, Class 1	Type III, Class 2
Non-volatile content	Report	X		X		X	
Removability	Completely removable with MIL-PRF-680 Type II or MIL-PRF-85570 Type II	X	X	X	X	X	X
Storage stability, minimum	Meets all specification requirements after one year from date of manufacture	X	X	X	X	X	X
Water displacement	No visible corrosion	X	X	X	X	X	X

1/ Unacceptable corrosion is more than three corrosion spots less than 1 mm in diameter, excluding the area within 1/8 inch of the panel edges or hole.

3.6.1 Self-pressurized containers. The containers shall conform to class 4, type IX of PPP-C-96 with valve opening diameter suitable for the specified valve. Neither the container nor any component thereof (closure, lining, etc.) shall interact with or alter the contents in any way so as to adversely affect their purity or quality. All containers shall be new and free from contaminants.

3.6.1.1 Net content. The net content of Class 1 containers shall be as specified in the contract or purchase order (see 6.2).

3.6.1.2 Marking. Marking of the containers shall be in accordance with MIL-STD-290, except as specified herein. Marking shall be legible, shall be accomplished by lithographing or silkscreen process and shall be in white on a bright green label for type III, class 2. Type I, class 2 shall be in white on blue background label. Type I, class 1, Type II, class 1; type III, class 1; and type II, class 2 may be marked in black on a white background or as specified in the contract or order (see 6.2). Paper coated labels on self-pressurized containers are not acceptable for the delivered product. Any special marking specified in the contract or order shall also be included. In addition, the following information shall be included on each self-pressurized container (when not already required by MIL-STD-290 or the contract or order):

Front Face: (Type I, class 2 only, Type II, class 2 only and type III, class 2 only):  
CORROSION PREVENTIVE COMPOUND, WATER DISPLACING,  
ULTRA-THIN FILM  
MIL-PRF-81309G  
PART NUMBER (see 1.3)  
CONTRACT NO.

MIL-PRF-81309G

MANUFACTURER'S NAME  
MANUFACTURER'S ADDRESS  
MANUFACTURER'S PRODUCT NO.  
NET WEIGHT

Rear Face:

CAUTION

FOR BEST RESULTS:

Hold can approximately 12 inches from the surface to be covered.

Spray a thin, uniform coating.

#### 4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

- a. Qualification inspection (see 4.3).
- b. Conformance inspection (see 4.4).

4.2 Inspection conditions. Standard conditions shall be a temperature of  $72 \pm 4$  °F and a relative humidity of  $50 \pm 20$  percent. All tests shall be conducted at standard conditions unless otherwise specified.

4.3 Qualification inspection. The qualification inspection shall consist of all the examinations and tests specified in Table II.

4.3.1 Health/hazard assessment (HHA). The product shall be evaluated by the Navy and Marine Corps Public Health Center (NMCPHC) using the administrative Health Hazard Assessment (HHA)(see 6.4).

## MIL-PRF-81309G

TABLE II. Qualification inspection and test methods.

Property	Requirement	Test Method
Acid salt fog protection	Table I	4.6.1
Application	Table I	4.6.2
Compatibility with polyimide, wiring insulation	Table I	4.6.3
Dielectric strength	Table I	4.6.5.1
Effect on acrylic plastic and polycarbonate	Table I	4.6.4
Effect on electronic components	Table I	4.6.5
Effect on urethane paint	Table I	4.6.6
Fill weight	Table I	4.6.7
Film appearance	Table I	4.6.8
Film thickness	Table I	4.6.9
Flame projection	Table I	4.6.20
Flash point	Table I	4.6.21
Friction coefficient	Table I	4.6.10
Functional penetration	Table I	4.6.11
Leakage/distortion of cans	Table I	4.6.12
Marking	3.6.1.2	Visual
Net content of container	3.6.1.1	4.6.19
Neutral salt spray protection	Table I	4.6.13
Non-volatile content	Table I	4.6.14
Performance of self-pressured container	3.6.1	4.6.15
Removability	Table I	4.6.16
Storage stability	Table I	4.6.17
Water displacement	Table I	4.6.18

## MIL-PRF-81309G

4.3.1 Qualification sample. The laboratory qualification sample shall consist of the following: for Class 1 (non-pressurized containers) - one gallon of the compound; for Class 2 (self-pressurized containers) - one gallon of the compound exclusive of propellants and five self-pressurized cans of the compound. Two quarts of each sample shall be set aside for the storage stability test. The samples shall be plainly identified by securely attached durable tags or labels marked with the following information:

MIL-PRF-81309 Sample for qualification inspection  
 CORROSION PREVENTIVE COMPOUND, WATER DISPLACING,  
 ULTRA-THIN FILM  
 Type and class for which qualification is desired  
 Name of manufacturer (plant in which material is manufactured)  
 Manufacturer's designation  
 Date of manufacture  
 Submitted by (name) (date) for qualification inspection in accordance with the  
 requirements of MIL-PRF-81309 under authorization (reference authorizing letter  
 (see 6.3).

4.4 Conformance inspection. The conformance inspections for the compound shall consist of tests specified in Table III.

TABLE III. Conformance inspection.

Property	Requirement	Test Method
Acid salt fog protection	Table I	4.6.1
Application	Table I	4.6.2
Fill weight	Table I	4.6.7
Film thickness	Table I	4.6.9
Flash point	Table I	4.6.21
Friction coefficient	Table I	4.6.10
Leakage/distortion of cans	Table I	4.6.12
Net content of container	3.6.1.1	4.6.19
Non-volatile content	Table I	4.6.14
Water displacement	Table I	4.6.18

## MIL-PRF-81309G

4.4.1 Conformance test samples. Conformance test samples shall be selected in accordance with Table IV. For Class 1, the sample unit for test shall be one quart of compound. For Class 2, the sample unit for test shall be one self-pressurized container and one quart of the compound used in these containers, exclusive of the propellant. Unless otherwise specified (see 6.2), samples shall be subjected to the tests specified in Table III (see 6.2).

4.4.1.1 Inspection of materials and components. The materials and components used shall be tested and inspected in accordance with the requirements of referenced subsidiary specifications and standards to the extent specified, or if none, in accordance with this specification.

TABLE IV. Conformance inspection samples.

LOT SIZE (UNITS)	SAMPLE SIZE (UNITS)
Up to 50	5
51 to 500	7
501 to 35,000	8
over 35,000	11

4.5 Test disks and panels.

4.5.1 Materials. The material for the test disks used for the acid salt fog protection test shall be carbon steel conforming to FS1020 of SAE AMS5046 for types I and II, or 410 stainless for type III. The material for the neutral salt spray protection test panels shall be 2024-T3 aluminum.

4.5.2 Size of test disks and panels. The aluminum test panels for the neutral salt spray protection test shall be 2 by 4 by 1/8 inch. The steel test disks for the acid salt fog test shall have a diameter of 2-1/8 inches and a thickness of 1/16-inch.

4.5.3 Preparation of test disks and panels. Remove all sharp edges and burrs and chamfer all holes to prevent injury in handling. Surface grind the panels and disks to 65 RMS, then hand polish them on one side and in one direction with a 240 grit silicon carbide or aluminum oxide cloth or paper. Do not use iron oxide or so-called "wet or dry" papers or cloths.

## MIL-PRF-81309G

4.5.4 Cleaning of test disks or panels. Do not handle disks or panels with bare hands. Use tongs and hooks to handle and do not allow them to contact contaminated surfaces. If preservative-treated test panels are obtained from a metal supplier in the above polished condition, wipe panels with cloth such as CCC-C-46 Class 7 or surgical gauze wet with acetone to remove preservative oils, repeat the wiping procedure with mineral spirits, then hand polish one side of the panel in one direction only with 240 grit silicon carbide or aluminum oxide cloth or paper. Wipe panels with the above cloth wet with acetone. Repeat the acetone wipe with a clean cloth. Finally, vapor degrease in methanol by dipping in vapor above boiling absolute methanol and allow to dry. Air dry in a rack and store in a desiccator until ready to use. If stored for more than 24 hours, repeat the surface preparation starting with hand polishing.

4.5.5 Coating of the disks or panels. Application of the compound to the test disks or panels shall be carried out under the conditions of 4.2. Pour a well-mixed representative sample of the compound into a clean dipping chamber of sufficient size to permit complete immersion of the disks or panels. To eliminate the formation of entrapped air bubbles, skim them from the top of the compound before immersing the disks or panels. Completely immerse the disks or panels vertically in the compound for one minute, then remove one at a time at a rate of 4 inches per minute. After removal, condition in a vertical position for 24 hours in a draft-, dust-, and fume-free atmosphere.

4.6 Test methods. Tests shall be conducted in accordance with the conditions specified in 4.2.

4.6.1 Acid salt fog protection.

4.6.1.1 Conditioning of compound sample. Fill a wide mouth, quart jar with 800 ml of the compound, seal, and expose to the following cycle four times without physical disturbance of the compound: eight hours at  $130^{\circ} \pm 2^{\circ}\text{F}$  followed by sixteen hours at  $-40^{\circ} \pm 2^{\circ}\text{F}$ . At the end of this cyclic exposure, allow the contents of the sealed jar to remain at  $75^{\circ} \pm 5^{\circ}\text{F}$  for 24 hours.

4.6.1.2 Test solution. The spray test solution shall consist of a solution made by adding 2 ml of sulfurous acid (6.4 percent assay as  $\text{SO}_2$ ) to each liter of synthetic seawater. Prepare the synthetic seawater by adding 50 grams of sodium chloride ( $\text{NaCl}$ ); 22 grams of magnesium chloride ( $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ ); 3.2 grams of calcium chloride ( $\text{CaCl}_2 \cdot 2\text{H}_2\text{O}$ ); and 8.0 grams of sodium sulfate ( $\text{Na}_2\text{SO}_4$ ) to a liter of distilled or demineralized water. Use 1500 mL of fresh test solution for each cycle. Measure the pH of the test solution. If the pH is not between 3.3 and 3.5, additional acid or synthetic seawater shall be added to adjust the pH to this range.

## MIL-PRF-81309G

4.6.1.3 Test procedure. The apparatus used in the test shall conform to Figures 1, 2, and 3. Prepare the test disks as specified in 4.5, using the conditioned compound in 4.6.1.1. Hang the disks vertically and dry for 24 hours under standard laboratory conditions (see 4.2). Insert the specimens into the turntable, start the turntable, and regulate the airflow to the nozzle to effect a fine spray. The pickup tube supplying the nozzle shall have an ID of 1 mm. At the end of approximately 2 minutes of spraying, fill each aluminum cup approximately one third full with ice and place on top of the disks to cause a fine condensation to form on the surface of the disks. Continue spraying for one hour. The rate of flow shall be approximately 1500 ml/hour. During this time, to avoid runoff washing over the test specimens, excessive condensation shall not be allowed to accumulate on the OUTSIDE of the aluminum cups. At the end of the hour, stop the spray, remove the aluminum cups, remove the jar from under the turntable, and allow the disks to dry at room temperature for 3 hours. Start another cycle with fresh test solution. Conduct two cycles in one day. After the required number of cycles, clean the disks in mineral spirits, conforming to MIL-PRF-680, then examine for any visible corrosion.

4.6.2 Application. For a Class 1 compound, place three ounces in a capped 4-ounce product jar conforming to SAE AS22805. Test Class 2 compounds as received. Condition the containers for 20 hours at 40 °F. For a Class 1 compound, remove product jar and contents from the cold chamber, immediately attach a spray device conforming to SAE AS22805 that has been conditioned at room temperature and attempt to spray the contents of the product jar. For Class 2 compounds, remove the self-pressurized container from the cold chamber and attempt to spray the contents. The compound passes the test if it can be satisfactorily sprayed. In addition, the applied compound shall not exhibit froth, bubbling, or excessive runoff and shall readily wet the surfaces of test panels prepared as in 4.5.

4.6.3 Compatibility with polyimide, wiring insulation. Approximately 24 inches (61 cm) of wire conforming to MIL-W-81381/11, shall be formed into a coil. Place coil in a 4-ounce (118 ml) wide mouth jar and add enough corrosion preventive compound to the jar to completely cover the coil of wire. Cap the jar and store it at room temperature for 14 days. Repeat this procedure using distilled water as the test medium. At the end of the storage period, remove the coil and rinse thoroughly with tap water at room temperature. Suspend the coil and allow it to drain until completely dry. Each wire shall be wrapped tightly around a 0.125-inch mandrel and unwrapped slowly, noting the appearance and number of any cracks in the insulation. The wire shall meet the requirements specified in Table I. The wire shall be immersed in a 5 percent by weight sodium chloride solution and subjected to a one-minute dielectric test of 2,500 volts (rms).

4.6.4 Effect on acrylic plastic and polycarbonate. Using ASTM F484, test the effects of the corrosion preventive compound on acrylic plastic (MIL-PRF-5425, Type A) and polycarbonate (SAE-AMS-P-83310). Test the compound by applying it to a 0.7 in. by 0.7 in. flannel swatch positioned on a loaded specimen (3,000 psi) immediately over the fulcrum point. After 30 minutes, examine the specimen. Crazing, cracking or other attack is not acceptable.

## MIL-PRF-81309G

4.6.5 Effect on electronic components. Connect a pair of electrical connectors, MS3116-16-26S and MS3112-16-26P. Determine the resistance using a Wheatstone Bridge or appropriate measuring device. Record the value for each mated pair of pins and between selected adjacent pins. Disconnect the connector and, while unmated, dip both connectors in the corrosion preventive compound three times with a two-hour interval between dipping. After 24 hours at the conditions described in 4.2, reconnect the connectors. Determine the resistance and record for each mated pair of pins and the selected adjacent pins. A change of more than 5 milliohms from the initial contact resistance is not acceptable.

4.6.5.1 Dielectric strength. The dielectric strength shall be tested in accordance with ASTM-D877.

4.6.6 Effect on urethane paint. Prepare painted test panels by priming suitably sized 0.020 in. thick aluminum panels with MIL-PRF-23377 primer and MIL-PRF-85285 gloss white urethane topcoat, in accordance with the specification directions, and allow to dry for a minimum of 4 weeks. Using the method and materials of ASTM F502, test the compound by applying it to approximately one half of a test panel positioned horizontally, painted side up, in an oven at 100 °F. After 30 minutes, remove the panel from the oven and remove the compound using MIL-PRF-680, type II dry cleaning solvent. After 24 hours, examine the panel and test the two halves for pencil hardness. Streaking, discoloration or blistering or loss of more than one unit of pencil hardness is not acceptable.

4.6.7 Fill weight. Weigh a sample can and then spray at three-minute periods with one-minute intervals until the can is exhausted. Reweigh the container. Determine the minimum net difference.

4.6.8 Film appearance. Mark a test panel, painted as in 4.6.6 and dried for 4 weeks, with two dots approximately 0.2 inch diameter, 0.5 inch apart, at the approximate center of the panel, using gray gloss enamel. Immerse the test panel in the compound so that the lower 2/3 of the panel is submerged. Remove the panel and dry it in a vertical position for 24 hours. After 24 hours, inspect the panel with the unaided eye and determine whether the simulated corrosion spots are visible through the coating.

4.6.9 Film thickness. The average film thickness produced by the compound shall be determined on a panel prepared, cleaned, and coated as specified in 4.5. Calculate the film thickness using the following formula:

$$\text{Film thickness (mils)} = \frac{(1.000 \times W) \times 0.061}{D \times A}$$

where: W = weight of film (grams).

0.061 cubic inch = 1 cubic centimeter.

D = density of the film, which shall be assumed = 1.0

A = total surface area of the panel (square inches).



## MIL-PRF-81309G

4.6.10 Friction coefficient.

4.6.10.1 Apparatus. The test apparatus (see Figures 4 and 5) shall consist of a 5 by 16 by 3/8-inch 2024 T6 SAE AMS-QQ-A-250/4 milled aluminum plate polished on the test side parallel with the longer dimension with 240 grit silicon carbide or aluminum oxide cloth or paper; a freely rotating wheel affixed to the plate by an axle parallel to the width approximately one inch from an end; a block holding 3 test balls in the configuration shown on Figure 5 and weighted in such a manner that each ball exerts a force equivalent to 250 grams on the surface of the aluminum plate; and a pan or beaker attached by a string over the pulley wheel to the three ball holder so that when taut the string is parallel to the plate surface. The test ball bearings shall be of 1/2-inch diameter AISI C-52100 steel, grade 25 extra polish (EP) quality steel balls of the American Bearing Manufacturer's Association.

4.6.10.2 Test procedure. Coat the upper surface of the aluminum plate with the compound to a thickness of 0.001 inch to 0.005 inch. Dry the coating at 72 °F for 24 hours. After drying, set the weighted three-ball holder gently on the coated surface at the end of the plate opposite the pulley wheel with one ball forward and two rearward. Orient so that if pulled by the string attachment toward the pulley wheel, no rotational motion occurs. Attach the pan or beaker as shown on Figure 5. Lightly drop test balls onto the pan from a height of less than 1/4-inch until the three-ball holder moves. If the holder traverses a distance of six inches in less than three seconds, record the gross weight of the pan. If the movement requires more than three seconds, place the holder as before at one end of the aluminum plate in a location different from those previous. Drop another test ball onto the pan from a height of less than 1/4-inch and observe the travel time. Repeat the restarting procedure until the three-ball holder travels six inches in less than three seconds. Record the gross weight of the pan. Determine the friction coefficient from the following equation:

$$\text{Friction coefficient} = \frac{\text{Gross pan weight}}{750\text{g}}$$

4.6.11 Functional penetration.

4.6.11.1 Specimen fabrication. Fabricate six panels and assemble three lap-joint specimens in accordance with Figure 6. Apply two strips of 2.0 by 0.5 by 0.20-inch vacuum bag sealing tape to one end of each lap joint assembly in accordance with Figure 7 and seal tightly.

## MATERIAL

## Test panels

7075 Aluminum, 0.125 by 3.0 by 8.0 inches, treated in accordance with MIL-DTL-5541, and primed in accordance with MIL-PRF-23377.

Bolt and collar fasteners

## MIL-PRF-81309G

4.6.11.2 Fluid penetration at room temperature. Support all three panel assemblies, with sealed areas at top, to maintain at an angle of 10 degrees from the horizontal (see Figure 7). Pour 1.0 ml of the compound to be tested, as-received bulk material or propellant-free material into the cavity formed by the sealing tape on each assembly. (NOTE: As an aid in the later identification of total faying surface penetration, an oil-soluble fluorescent dye, fluoro-green gold, or equivalent, may be dissolved in the compound to be tested provided the concentration does not exceed 8.0 mg/100 cc.) After 24 hours, remove the residual fluid from the cavity with clean, dry cheesecloth. Immediately remove sealing tape and wipe all four-perimeter edges of the faying surface with clean filter paper to remove residual test fluid. Edge clamp each assembly and remove fasteners. Open each assembly with care and determine the percentage of each faying surface area that has been wetted by the test fluid – a 3.0 by 2.0 inch transparent grid, with twenty five squares per inch, may be held above the surface to facilitate measurement of the wetted area.

4.6.12 Leakage or distortion of cans. Completely submerge the self-pressurized container for 5 minutes in water maintained at a minimum of  $130^{\circ} \pm 2^{\circ}\text{F}$ . Observe for the emission of bubbles. Distortion of the container or the emission of bubbles from any part of the container is cause for rejection.

4.6.13 Neutral salt spray protection. Test panels prepared and coated as specified in 4.5 shall be subjected to ASTM B117 salt spray exposure. Incline three specimens at  $6^{\circ}$  in a rack. After 336 hours, clean test panels in solvent, conforming to MIL-PRF-680, and examine for any visible corrosion. Unacceptable corrosion is more than three corrosion spots less than 1 mm in diameter, excluding the area within 1/8 inch of the panel edges or hole.

4.6.14 Nonvolatile content. Place a portion of the thoroughly mixed sample in a stoppered bottle, or alternatively, in a weighing pipette or a 10 ml syringe without a needle, and from this weigh by difference  $1.2 \pm 0.1$  grams into a suitable aluminum weighing dish 80 to 100 mm in diameter and 5 to 10 mm in depth. By gentle tilting, spread the specimen over the bottom of the dish and heat for 3 hours in a ventilated oven maintained at  $221 \pm 3^{\circ}\text{F}$ . If necessary, a piece of stout wire can be included in the tare of the dish and used at intervals to break up skins by stirring during the heating period. Cool in a desiccator and weigh the dish. Calculate the percent nonvolatile matter to the nearest 0.1 percent, as follows:

$$\text{Percent nonvolatile matter} = \frac{\text{Net weight of residue}}{\text{Net weight of original sample}} \times 100$$

## MIL-PRF-81309G

4.6.15 Performance of Class 2 self-pressurized containers. The rectangular panels prepared in accordance with 4.5 shall be used. Support a panel such that the longer dimension forms a 45° angle with the horizontal. Spray corrosion preventive compound on the panel from a distance of 12 inches. Examine the panel for uniformity of spray, foaming, and adherence to the substrate. After a 10 second pause, respray the same panel and examine for adhesion and sagging. After a 5 second pause, respray the same panel and examine for adhesion and sagging. The container shall be checked for conformance with 3.6.1.2.

4.6.16 Removability. Dry the coated test panel from 4.6.8 for 24 hours at 72 °F. Attempt to remove the compound by wiping the coated surface using light hand pressure with a CCC-C-46 Class 7 wiping cloth dampened with 10 milliliters of MIL-PRF-680, Type II or MIL-PRF-85570 Type II properly diluted. In daylight, from 6 feet away, there shall be no visual evidence of residue.

4.6.17 Storage stability. Pour two liters of the material into a clean and dry glass jar. Tightly cap the jar and wrap it in aluminum foil to exclude all light from the sample. Store the sample for one year in a constant temperature chamber at 75 ±6 °F. At the end of the one year period, remove the jar from the chamber and take off the aluminum foil. Visually inspect the sample and note the presence of cloudiness, sediment, suspended matter, or other changes in homogeneity. The stored sample shall be tested for conformance to all the requirements in this specification (excluding storage stability).

4.6.18 Water displacement. Place an uncoated panel (prepared as specified in 4.5) so that one 2-inch end shall be raised one inch above a horizontal surface. Spray the panel with the unacidified synthetic sea water of 4.6.1.2 so that its entire upper surface is covered with tiny droplets. Within one-minute after spraying, pour one milliliter of the test compound along the upper edge of the panel and allow to run slowly down so as to completely cover the test panel. After another minute, pour a second milliliter of the test compound and allow to run down in a like manner. After waiting an additional minute, raise the panel to a vertical position for one minute and then place flat (test side up) above distilled water at 72 °F in a closed desiccator. After 4 hours, remove the panel, clean with mineral spirits, then evaluate for presence of visible corrosion.

4.6.19 Net content. The sample unit for this examination shall be one filled container. The sample size shall be as specified in Table IV. The lot is unacceptable if the average net content per container for all units examined is less than specified.

4.6.20 Flame projection. The flame projection shall be tested in accordance with ASTM D3065.

4.6.21 Flash point. The flash point shall be tested in accordance with ASTM D93.

## MIL-PRF-81309G

## 5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

## 6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The ultra-thin film, corrosion preventive compound covered by this specification is intended for use on any metal surface. It can be used both for initial protection during shipment and storage and for in-service treatment. It should not be used around liquid oxygen fittings. The ability of this material to prevent corrosion and to displace water and its ease of application when packaged as class 2 (self-pressurized containers) make it particularly suited for service use. The combination of properties of MIL-PRF-81309 provide the necessary requirements for a corrosion preventing compound for use in the extreme naval aviation environment. This material is intended for indoor protection and short term protection outdoors where surfaces can be recoated when required. This material is not intended as a substitute for other corrosion preventatives specified for protection of surfaces for periods of more than one month.

6.1.1 Type I, class 1 and 2. This type is designed to inhibit mildew growth and prevent corrosion simultaneously. This type is intended for use on moving parts where some lubrication is required, such as hinges, bomb racks, and sliding parts.

6.1.2 Type II, classes 1 and 2. This compound is intended for use on moving parts where some lubrication is required, such as hinges, bomb racks, and sliding parts.

6.1.3 Type III, classes 1 and 2. The compound is intended for use on avionic equipment, electrical connector plugs, and contact points.

6.2 Acquisition requirements. Acquisition documents should specify the following:

- a. Title, number, and date of this specification.
- b. Type, class and grade of compound (see 1.2).
- c. Unit of issue required.
- d. Quantity. (For non-pressurized container specify gallons; for self-pressurized

## MIL-PRF-81309G

containers specify number of cans).

- e. Net content (see 3.6.1.1)
- f. Special marking requirements (see 3.6.1.2).
- g. Certified test report with each lot showing that the lot conforms to the specification (see 4.4.1).
- h. Packaging requirements (see 5.1).

6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Products List (QPL-81309) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from Commander, Naval Air Warfare Center Aircraft Division, Code 4.3.4.2, 48066 Shaw Road, Bldg 2188, Unit 5, Patuxent River, MD 20670-1161, e-mail [todd.standish@navy.mil](mailto:todd.standish@navy.mil). An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at <https://assist.dla.mil>.

6.3.1 Manufacturer's qualification data. In addition to the qualification sample, the manufacturer will submit: 1) a Material Safety Data Sheet prepared in accordance with FED-STD-313 and 29 CFR 1910.1200, 2) a report that includes the results of any tests performed by the manufacturer, 3) certification that product meets the requirements of 3.5 for mildew inhibitor additive 4) certification that the compound meets the storage stability requirement, 5) certification that the compound meets the toxicity requirements of 3.3, and 6) for Class 2 compounds, a description of the aerosol container construction (including type and model numbers for the can, valve, and spray head).

6.4 Toxicity evaluation. A flowchart for the HHA process can be found as enclosure (1) of BUMEDINST 6270.8. The HHA is a review of the product based on information submitted by the manufacturer, to assess health hazards associated with the handling, application, use and removal of the product. Sufficient data to permit an HHA of the product should be provided by the manufacturer/distributor to the NAVENVIRHLTHCEN. To obtain current technical information requirements specified by the NAVENVIRHLTHCEN or any questions concerning toxicity, information required to conduct a HHA, and requests for a HHA should be addressed to the Commanding Officer, Navy and Marine Corps Public Health Center, ATTN: Hazardous Materials Department, Industrial Hygiene Directorate, 620 John Paul Jones Circle, Suite 1100, Portsmouth, VA 20378-2103. Upon receipt of the HHA, a copy should be provided to Commander, Naval Sea Systems Command, ATTN: SEA 05M1, 1333 Isaac Hull Ave., SE, Stop 5133 Washington Navy Yard, DC 20376-5133.

6.5 NAVSEA List of Targeted Chemicals. Materials and products utilized in this specification should be absent of chemicals listed on the NAVSEA List of Targeted Chemicals (N-LTC, ETAP 3.7.5.2). These chemicals pose significant risk to the user and/or the

## MIL-PRF-81309G

environment, and are deemed both undesirable and unsustainable by NAVSEA Technical Authority. NAVSEA is minimizing the use of Hazardous Materials in the Design and Development of its assets. It is recommended that alternative materials be considered for associated applications, so as to minimize the integration of targeted chemicals in NAVSEA assets delineated in this specification.

## 6.6 Definitions.

6.6.1 Batch. A batch is defined as that quantity of material which has been manufactured by some unit chemical process and subjected to some physical mixing operation intended to make the final product substantially uniform.

6.6.2 Lot. A lot is defined as all the compound produced by one manufacturer, at one plant, from the same materials, and under essentially the same conditions during a continuous operation not exceeding 24 hours. In the event the process is a batch (see 6.6.1) operation, each batch will constitute a lot.

6.6.3 Solvent. A solvent is defined as an organic liquid having a vapor pressure of greater than 0.1 mm Hg at 25 °C.

6.7 Material safety data sheets. Contracting officers will identify those activities requiring copies of completed Material Safety Data Sheets prepared in accordance with FED-STD-313. The pertinent government mailing addresses for submission of data are listed in Appendix B of FED-STD-313.

6.8 Relationship of this specification to previous issues. MIL-C-81309A provided two grades of soft film corrosion preventive compound; grade A for use on all metals and grade B for use on stainless steel and aluminum in interior locations. MIL-C-0081309B(AS) provided one grade of dry-to-touch compound which can be used on all metals. Under both of these specifications bulk material or self-pressurized spray (aerosol) cans were acquired on order but were not classified separately. MIL-C-0081309C(AS) provided for both dry-to-touch films and soft film compounds for application as described in 6.1. In addition, provision was made to facilitate the acquisition by defining separate classes for bulk or self-pressurized containers (aerosols). MIL-C-81309D deleted type I, class 1 and 2 compounds which have been superseded by MIL-C-85054. MIL-C-81309E does not alter the type and class arrangement of MIL-C-81309D; however, propellants used in self-pressurized containers as substitutes for CFCs have been included as Grades 22 and 134a. The equivalents are specified in Table V. MIL-PRF-81309F deleted Grade 22, added Grade CO<sub>2</sub>, and modified corrosion requirements.

## 6.9 Subject term (key word) listing.

Avionics  
Brushable  
Carbon dioxide propellant

## MIL-PRF-81309G

Dip  
 HCFC propellant  
 HFC propellant  
 Mildew inhibitor  
 Self-pressurized containers  
 Soft film  
 Sprayable

6.10 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.


TABLE V. Table of equivalents.

Type	Class	MIL-C-81309 Revision Letter						
		G	F	E	D	C	B	A
I	1	Included	Not included	Not included	Superseded by MIL-C-85054 type II	Type I, class 1	Bulk	-
I	2	Included	Not included	Not included	Superseded by MIL-C-85054 type I	Type I, class 2	Self-pressurized container	-
II	1	No change	No change	No change	Type III, class 2	Type II, class 1	-	Grades A and B - bulk
II	2	No change	No change	No change	Type II, class 2	Type II, class 1	-	Grade A self-pressurized container
III	1	No change	No change 1/	No change 1/	Type III, class 1	Type III, class 1	-	Grade B bulk
III	2	No change	No change 1/	No change 1/	Type III, class 2	Type III, class 1	-	Grade B self-pressurized container

1/ Choice of Grades for self-pressurized containers (see 1.2.3).



MIL-PRF-81309G

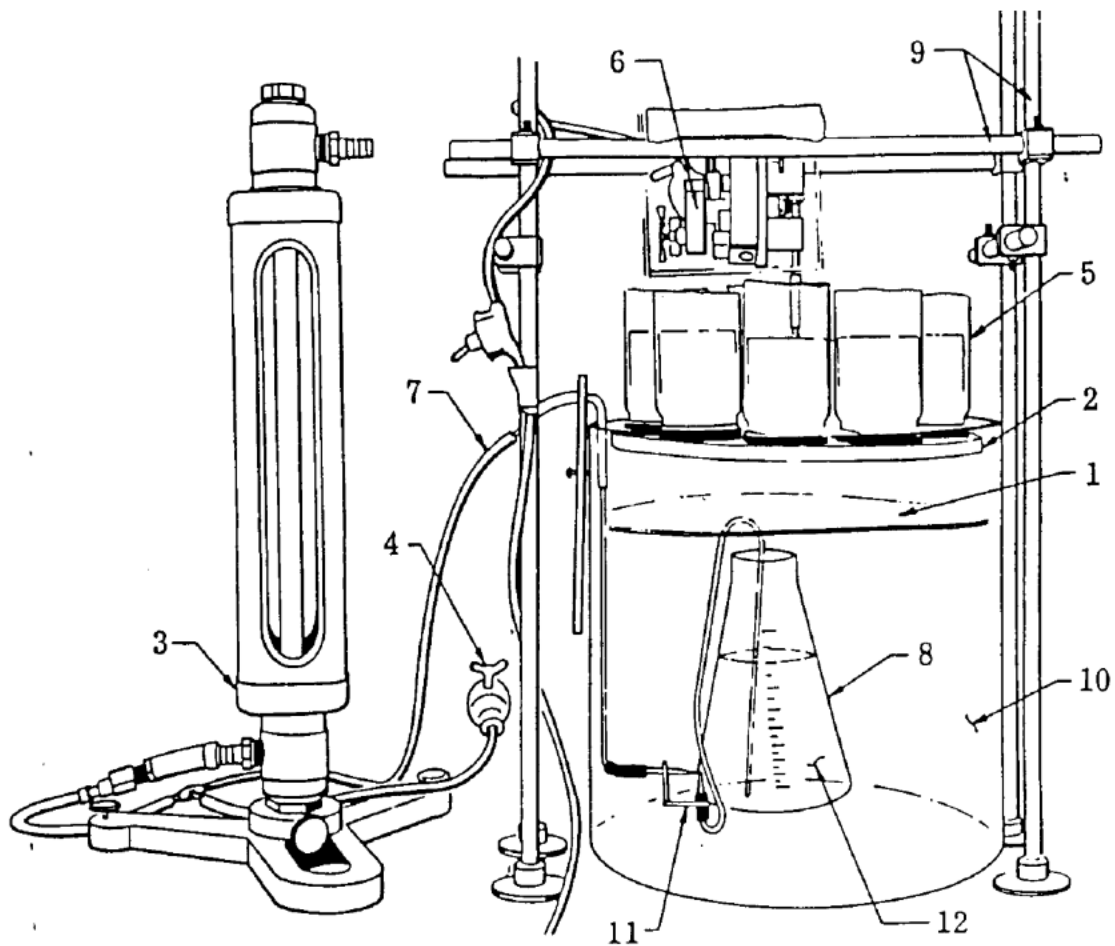FIGURE 1. Acid salt fog protection test apparatus.

## NOTES:

1. Acrylic Baffle - 12 inches in diameter or snug fit in a jar (10) with a 3 inch diameter center hole. The baffle is located within the jar (10) above the spray nozzle (11), thus preventing direct impingement of the spray on the disks, but allowing the fine spray mist full contact with the disks under test. Edge of baffle shall be notched to allow passage of the tube leading to spray nozzle (11).
2. Acrylic Turntable - 10-1/2 inches in diameter, positioned approximately 1/2 inch below the top of the jar (10). The turntable is provided with holes for the mounting of the test disk holders (5) and disks. The turntable is mechanically rotated, driven by an electric motor (6) (encased within a protective acrylic box, mounted above the jar (10) on an arrangement of Flex-frame support rods (9)).
3. Air Regulator.



## MIL-PRF-81309G

4. Air Source
5. Coated Test Disk Holder (see figure 3).
6. Electric motor (slow speed one rpm or less).
7. Filtered air source - with an air regulator (3) capable of regulating the air flow to the to the spray nozzle (11) at one cubic foot per minute.
8. Flask – 1000 ml, extra wide mouth, Erlenmeyer flask, placed in the jar (10) to hold the synthetic sea water sulfurous acid solution.
9. Flex frame support rods.
10. Jar - 12 inches in inside diameter and 12 inches high.
- 11 Spray Nozzle - see figure 2.
12. Test Solution.

MIL-PRF-81309G


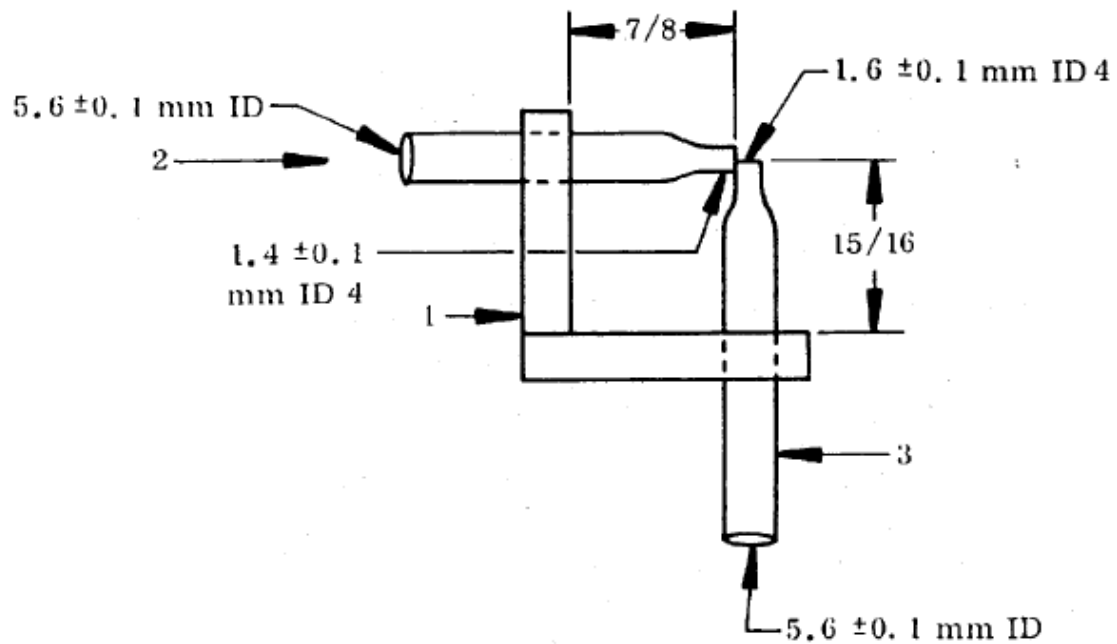


FIGURE 2. Spray nozzle.

## MIL-PRF-81309G

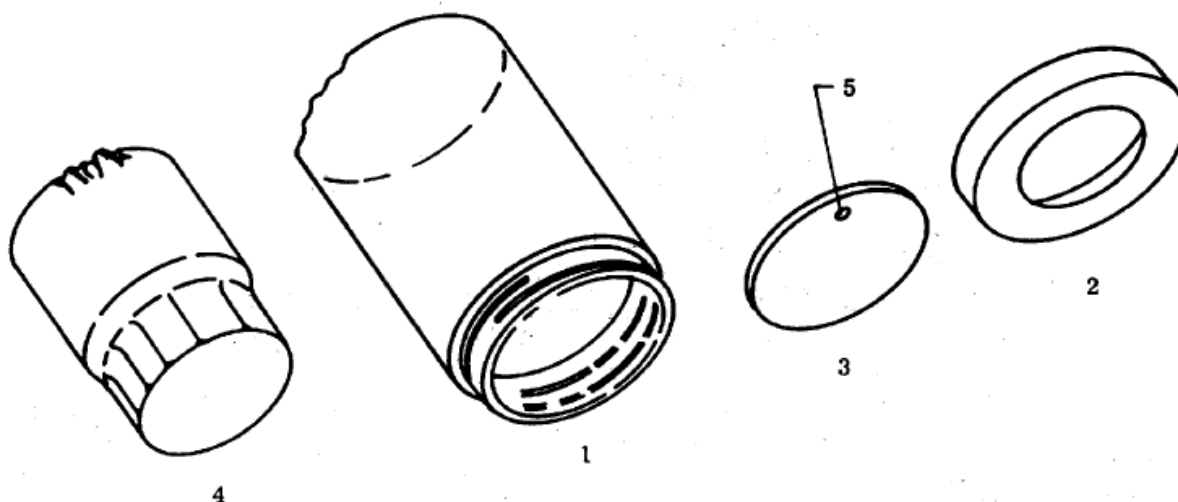

## NOTES:

1. Disk holder.
2. Disk holder cap.
3. Test disk - A 1/32 inch diameter hole (5) is provided for handling the disk by stainless steel wire.
4. Water jacket- In use, the aluminum water jacket is placed so as to be in direct contact with the back of the round test disk (3).

General - The complete test disk holder, with disk, described above, is mounted in one of the holes of the acrylic turntable of the apparatus on figure 1 (see notes 2 and 5, figure 1).

FIGURE 3. Water jacket; test disk, holder and cup.

MIL-PRF-81309G

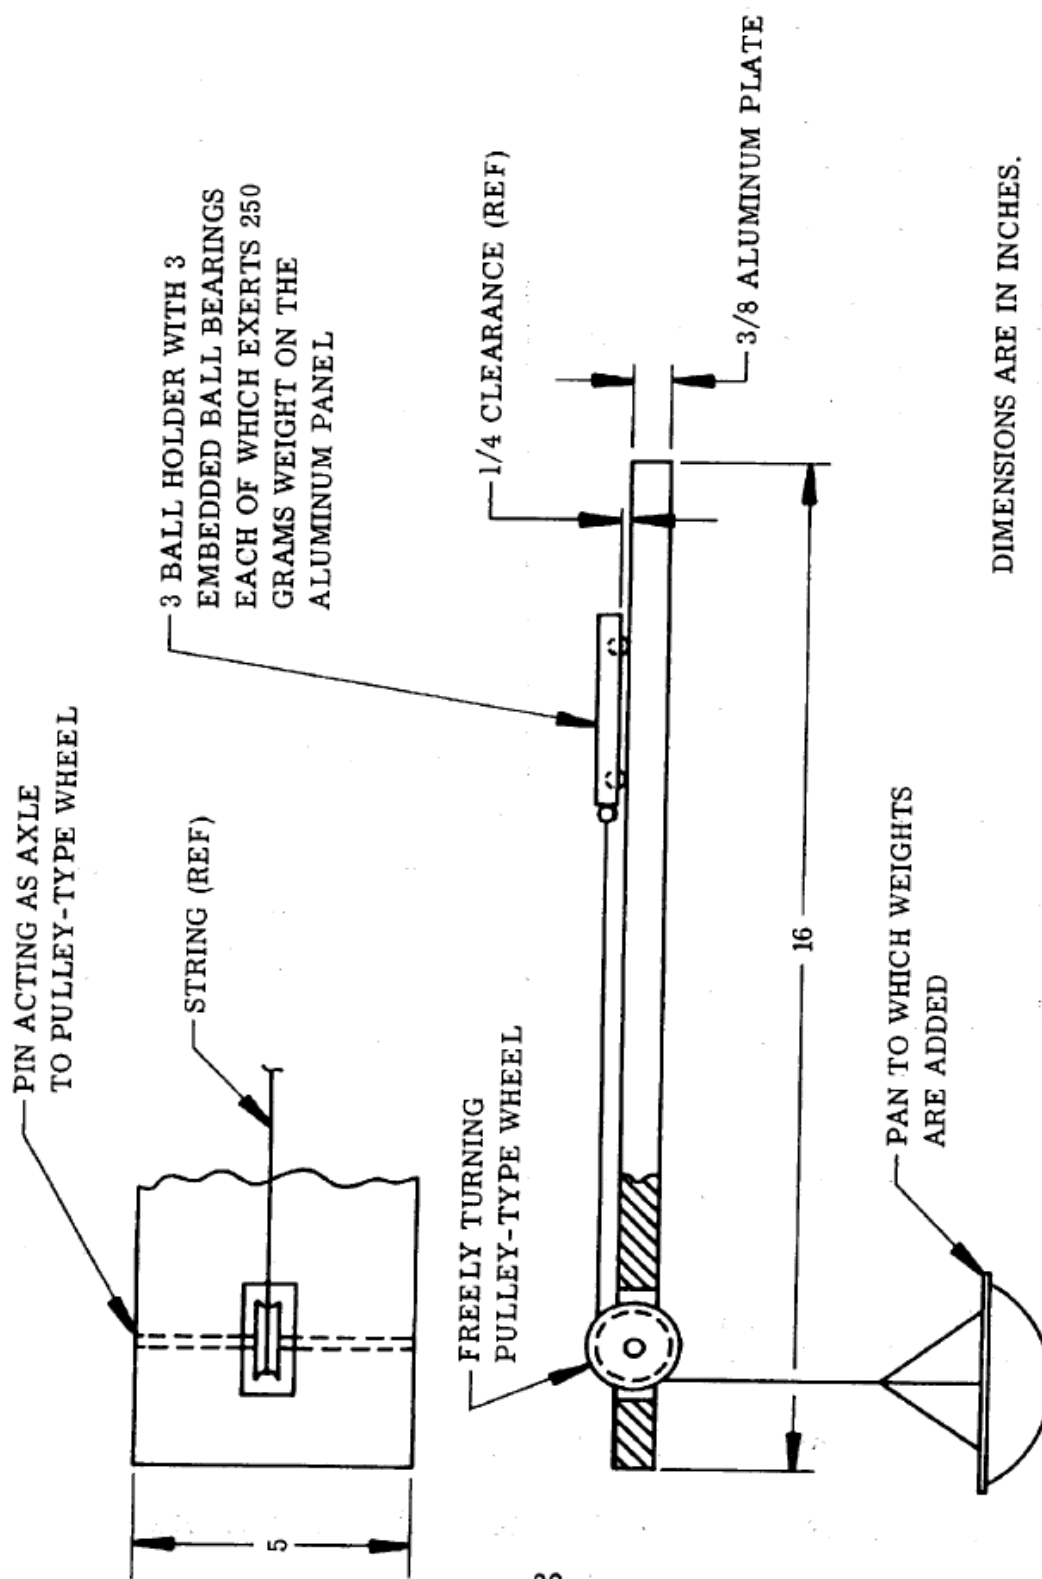
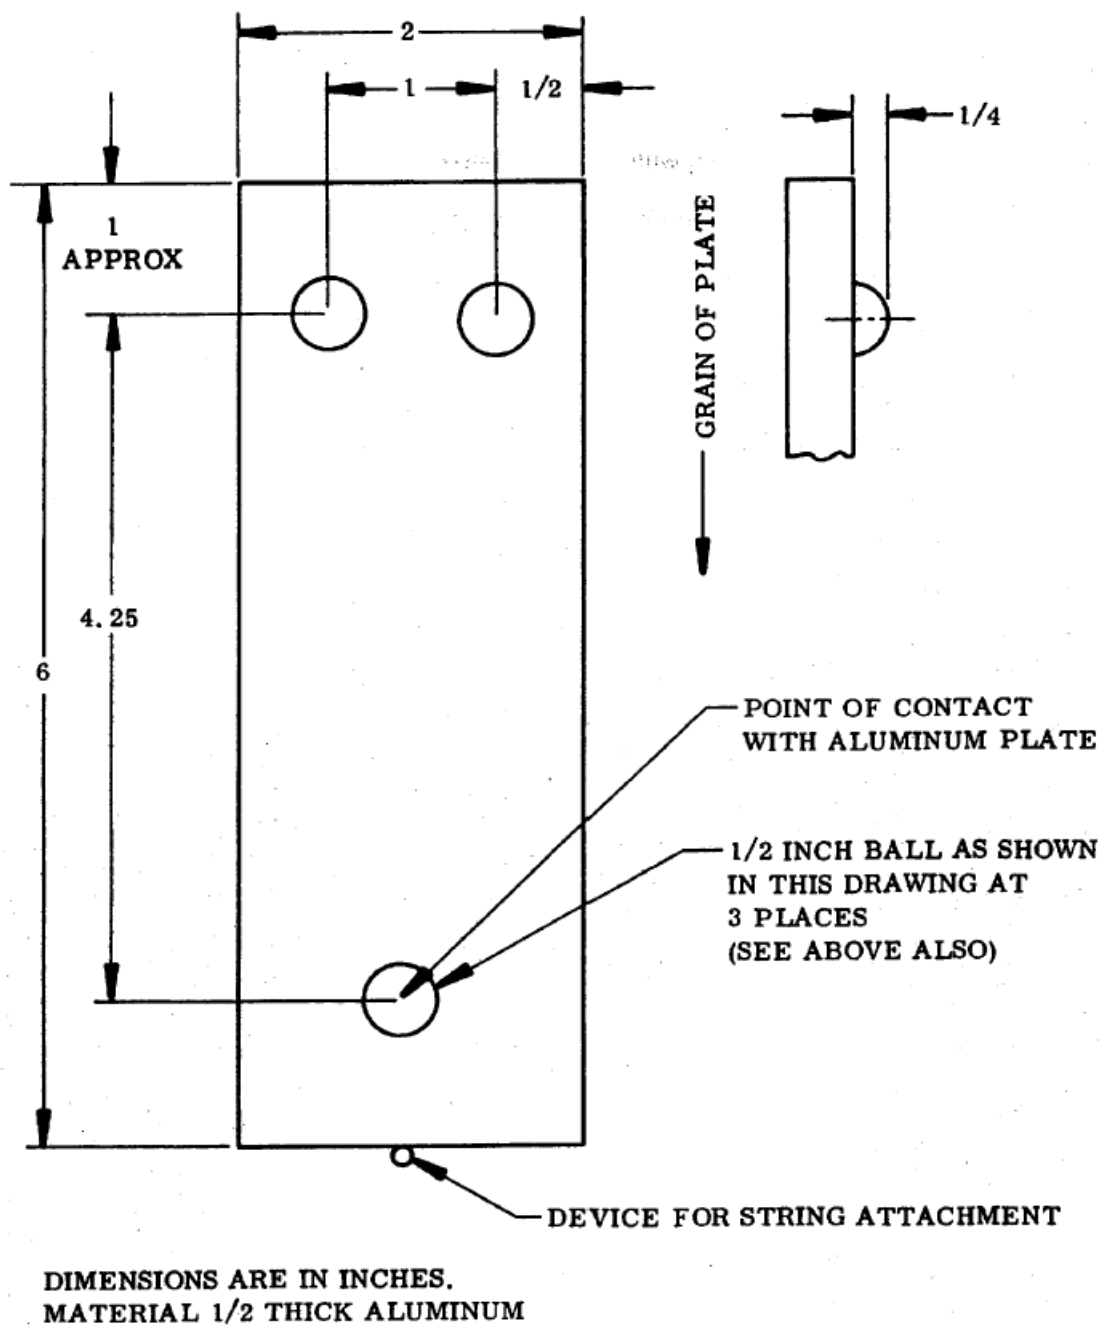


FIGURE 4. Apparatus for determining lubricity.

MIL-PRF-81309G

FIGURE 5. Bottom view of aluminum plate on the lubricity apparatus.

## MIL-PRF-81309G

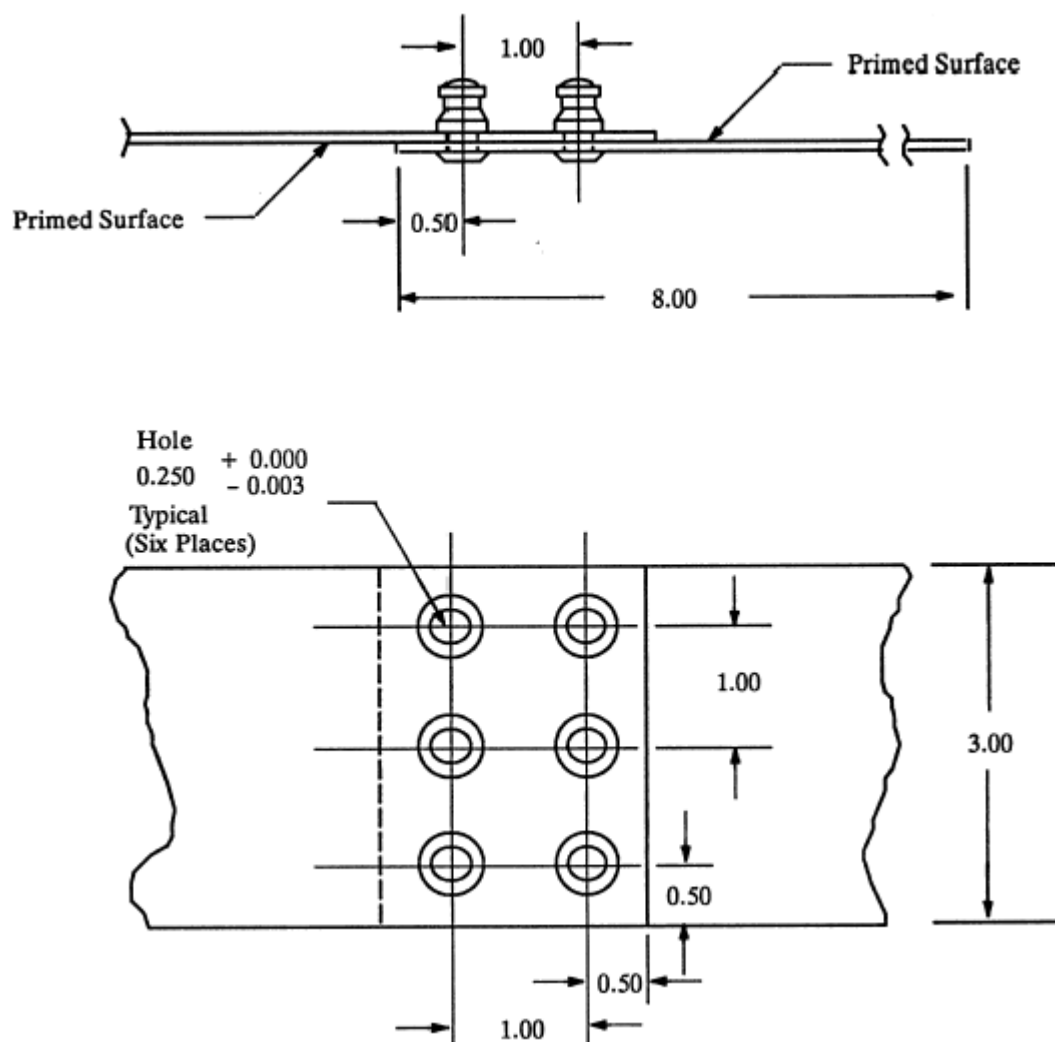


FIGURE 6. Penetration panel assembly.

MIL-PRF-81309G

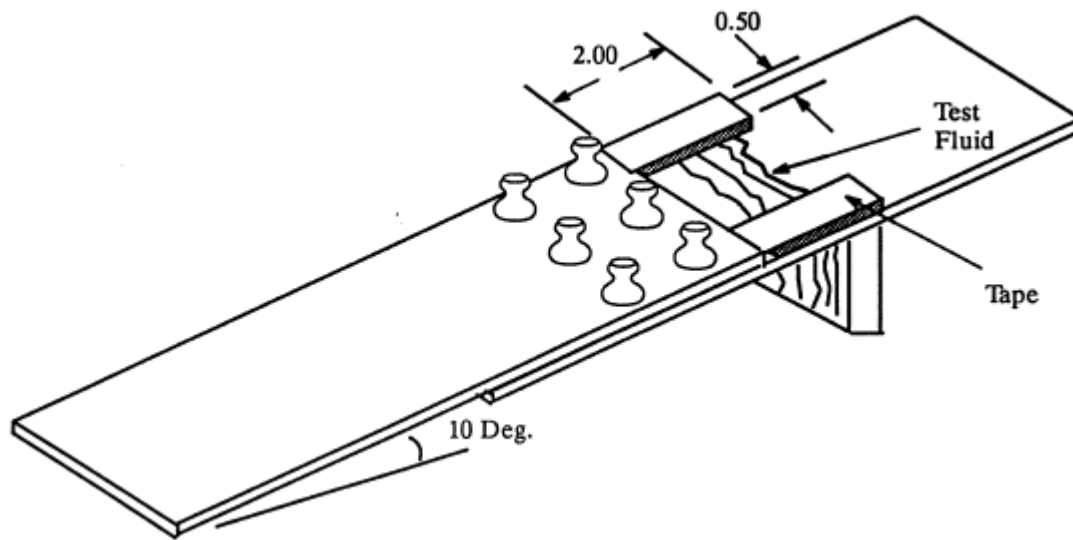


FIGURE 7. Functional penetration configuration.

MIL-PRF-81309G

## CONCLUDING MATERIAL

**Custodians:**

Army - EA

Navy - AS

Air Force - 99

**Preparing activity:**

Navy - AS

(Project 8030-2014-005)

**Review activities:**

Army - AT, MR

Navy - CG, OS

Air Force - 84

Other agency - DS

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at <https://assist.dla.mil>.