

INCH - POUND

MIL-B-62346C(AT)  
10 December 1990  
 SUPERCEDING  
 MIL-B-62346B(AT)  
 14 January 1988

## MILITARY SPECIFICATION

BATTERIES, STORAGE: LEAD-ACID  
 (LOW MAINTENANCE)

This specification is approved for use within the U.S. Army Tank-Automotive Command, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.

## 1. SCOPE

1.1 Scope. This specification covers one type of waterproof, low maintenance, lead-acid battery furnished in charged and dry or charged and wet condition.

<u>TYPE</u> <u>DESIGNATION</u>	<u>VOLTAGE</u>	<u>RATED RESERVE</u> <u>CAPACITY (MIN)</u>	<u>AMPERE-HOURS</u> <u>(20-HOUR RATE)</u>
6TL	12	200	120

Beneficial comments (recommendations, additions, deletions) and any other pertinent data which may be of use in improving this document should be addressed to: U.S. Army Tank-Automotive Command, ATTN: AMSTA-GDS, Warren, MI 48397-5000, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document, or by letter.

AMSC N/A

FSC 6140

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

## MIL-B-62346C(AT)

## 2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. The following specifications and standards form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation.

## SPECIFICATIONS

FEDERAL  
0-S-801

- Sulfuric Acid, Electrolyte; for  
Storage Batteries

MILITARY  
MIL-B-208

- Battery, Storage, Lead Acid,  
Automotive and Navy Portable  
(Except Aircraft), Packaging and  
Packing of

## STANDARDS

FEDERAL  
FED-STD-595

- Colors

MILITARY  
MIL-STD-129  
MIL-STD-202

- Marking for Shipment and Storage  
- Test Methods for Electronic and  
Electrical Component Parts

MIL-STD-45662  
MS52149

- Calibration System Requirements  
- Battery, Storage, Lead-Acid (Low-  
Maintenance), Type 6TL

2.1.2 Other Government Documents. The following other Government documents form a part of this specification to the extent specified herein. Unless otherwise specified, the issues shall be those in effect on the date of the solicitation.

MIL-B-62346C(AT)

DEPARTMENT OF TRANSPORTATION (DOT)

Federal Motor Carrier Safety Regulations (FMCSR) -  
49 CFR

(Application for copies should be addressed to the Department of Transportation, Washington, D.C. 20590.)

(Copies of specifications, standards and other Government documents required by the contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting activity.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of the documents, which are DOD adopted, shall be those listed in the issue of DODISS specified in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS shall be the issue of non-Government documents which is current on the date of the solicitation.

UNIFORM CLASSIFICATION COMMITTEE

Consolidated Freight Classification Rating, Rules and Regulations

(Application for copies should be addressed to the Uniform Classification Committee, 22 South Riverside Plaza, Chicago, IL 60606.)

SOCIETY OF AUTOMOTIVE ENGINEERS (SAE)

SAE J537i - Storage Batteries

SAE J1495 - Test Procedure for Battery  
Flame Retardant Venting Systems

(Application for copies should be addressed to the Society of Automotive Engineers, 400 Commonwealth Drive, Warrendale, PA 15096.)

(Non-Government standards and other publications are normally available from the organizations which prepare or which distribute the documents. These documents also may be available in or through libraries or other informational services.)

## MIL-B-62346C(AT)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein (except for associated detail specifications, specification sheets or MS standards), the text of this specification shall take precedence. Nothing in this specification, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

## 3. REQUIREMENTS

3.1 Specification sheets. The individual item requirements shall be as specified herein and in accordance with the applicable specification sheet. In the event of any conflict between the requirements of this specification and the specification sheet, the latter shall govern.

3.2 Qualification. The battery furnished under this specification shall be a product which is qualified for listing on the applicable Qualified Product List (QPL) at the time set for opening of bids (see 4.6 and 6.3).

3.3 Materials. Materials shall be as specified herein and in referenced specifications, standards and drawings. Material shall be free of defects adversely affecting performance or serviceability of the finished product.

3.3.1 Electrolyte. The electrolyte, used in filling batteries, shall conform to Class 3 of 0-S-801.

3.3.2 Active material. Active material reclaimed from plates of other batteries shall not be used.

3.3.3 Recycled, virgin and reclaimed materials. There are no requirements for the exclusive use of virgin materials. The use of recycled or reclaimed (recovered) materials is acceptable, provided that all other requirements of this specification are met (see 6.5.1).

3.4 Construction. Batteries shall be constructed in accordance with MS52149. Battery shall be furnished as a complete, integral assembly, with no loose parts permitted, except for the vent filler plugs as specified in 3.5.8.

## MIL-B-62346C(AT)

3.4.1 Containers. Containers shall be molded to the dimensions specified in MS52149. The containers shall be free of leaks, blisters, cracks, or other defects that could adversely affect the performance of the battery. Container color shall be lusterless olive drab, conforming to color chip number 34088 of FED-STD-595. The container shall be made from non-absorbent, acid-resistant, thermoplastic material meeting the physical requirements specified in 3.5.1 through 3.5.4.

3.4.2 Battery cover. Battery cover shall meet the same physical and color requirements as the container material. Battery cover shall be of one piece design and shall be sealed to the container, thereby forming a case. Cover and base are to be parallel within 0.060 inch, total. The seal shall maintain an acid tight joint between case and cover under all test conditions specified herein (see 4.8.6).

3.5 Physical requirements.

3.5.1 Electrical breakdown. The battery container shall withstand an alternating current potential of 100 volts (V) root mean square (RMS) per mil of thickness without damage (see 4.8.1).

3.5.2 Acid absorption. The battery container material shall exhibit no cracks or blisters, no more than 1.5 percent increase in weight, and no more than 2 percent increase in any physical dimension in a 1.300 specific gravity electrolyte solution at  $150^{\circ} \pm 2^{\circ}$  F ( $65.6^{\circ} \pm 1^{\circ}$  C) for a period of seven days (see 4.8.2).

3.5.3 Impact resistance. Twenty-four hours or more after manufacture, the sample battery case shall exhibit minimum impact resistance after four hours pre-test conditioning at temperatures in Table I (see 4.8.3).

TABLE I. Impact resistance

<u>PRE-TEST CONDITIONING TEMPERATURE</u>	<u>IMPACT RESISTANCE (INCH-POUNDS)</u>
150° F ( 65.6 ° C)	180
0° F (-17.8 ° C)	120
-40° F (-40° C)	60

## MIL-B-62346C(AT)

3.5.4 Bulge resistance. Battery container shall exhibit no more than 1/4 inch bulge after exposure to  $200^{\circ} \pm 5^{\circ} \text{ F}$  ( $93.3^{\circ} \pm 3^{\circ} \text{ C}$ ) for three hours (see 4.8.4).

3.5.5 Filler plug openings. The battery cover shall contain a threaded vent filler plug opening for each cell (see 3.5.8). The vent filler plug openings shall be designed to permit easy determination of the electrolyte level. Electrolyte level instructions shall be plainly marked, either on the battery cover or on the vent filler plug.

3.5.6 Post seals. Post seals shall maintain an unbroken seal between post and cover and shall show no indication of leakage under any of the test conditions specified herein.

3.5.7 Cell seals. Cells shall be sealed by easily removable, air tight, and moisture proof seals, not an integral part of the battery cover, which shall retain their seal and hold firmly in place until intentionally removed. Dummy vent filler plugs may be used provided the proper plugs are packaged with the battery.

3.5.8 Vent filler plugs. Non-absorbent, acid resistant filler plugs shall be provided for each cell. Design shall be as specified on MS52149. The vent filler plugs shall be of the submersible type and shall incorporate a vent with a check valve to permit the escape of gasses from the battery. Vent plugs shall not permit ignition of flammable gasses in the test fixture when tested in accordance with 4.8.7.1. The check valves shall not leak more than two drops of water in 10 seconds when under a four foot head of water and shall be designed to open before internal pressure reaches 0.5 pounds per square inch (psi) in excess of the external pressure. The plugs shall withstand temperatures from  $-65^{\circ} \text{ F}$  ( $-53.9^{\circ} \text{ C}$ )  $9^{\circ} \text{ C}$ ) to  $+250^{\circ} \text{ F}$  ( $121^{\circ} \text{ C}$ ) without cracking, melting or other damage (see 4.8.7).

3.5.9 Handles. Handles shall be rope type plastic of the developed length specified in MS52149. Handles shall withstand the effects of electrolyte conforming to the Class 3 of O-S-801 (see 3.3.1). Each handle shall be attached to the battery case in such a manner as to withstand, without damage to the case, the handle, or the attachment, when tested in accordance with 4.8.8 at temperatures of  $190^{\circ} \pm 2^{\circ} \text{ F}$  ( $88^{\circ} \pm 1^{\circ} \text{ C}$ ) and  $-65^{\circ} \pm 2^{\circ} \text{ F}$  ( $-54^{\circ} \pm 1^{\circ} \text{ C}$ ) (see 4.8.8). If knots are used to secure rope handle, they shall be melted to prevent untying.

## MIL-B-62346C (AT)

3.5.10 Grids and plates. Grids shall have no framing bars cracked, broken or missing. After pasting of active material, plates shall evidence not more than three through holes in the active material. Plates shall have no open windows.

3.5.10.1 Plates. Plates shall be of the pasted type and the grid lead alloy shall contain no antimony. Optional construction: Negative plate grids shall have non-antimony or low percent (not to exceed 1.0 percent) antimony and positive plate grids not to exceed 3.5 percent antimony.

3.5.11 Plate connections and intercell connectors. Plates of like polarity in each cell shall be integrally joined by intercell connectors. The intercell connectors shall be of the burned-on, cast-on, or welded type. Each connector shall be of such size and strength as to provide both electrical conduction and support for each group of like polarity plates. Plate-connecting intercell connectors of the up and over type shall not be used.

3.5.12 Separators. Separators shall be an envelope type, enclosing the positive plates and shall extend a minimum of 3/32 inch above plates after assembly.

3.5.13 Terminal posts. Terminal posts shall be of the design and location specified on the applicable specification sheet. The positive tapered terminal post shall be identified by a "+", a "POS", or a "P" and the negative terminal by a "-", a "NEG", or a "N" as shown on the applicable specification sheet. All metal parts of the terminal shall be lead or lead coated (See MS52149).

3.5.13.1 Terminal post torque resistance. Tapered terminal posts shall withstand, without damage to the battery, a torque of 250 inch-pounds (see 4.8.9).

3.6 Battery condition. Batteries shall be furnished in a condition in accordance with MS52149 (see 6.2).

3.6.1 Charged and dry. Batteries furnished in the charged and dry condition shall contain dry plates and separators. The moisture content of the separators shall not exceed 3.0 percent. The moisture content of the plates shall

## MIL-B-62346C(AT)

not exceed 0.2 percent. No electrolyte shall be furnished (see 4.8.10).

3.6.1.1 Dry cell internal resistance. The terminal-to-terminal resistance of each cell, measured after assembly in the container with the top off, shall be no less than 50,000 ohms.

3.6.2 Charged and wet. Batteries furnished in the charged and wet conditions shall be filled to the proper level with electrolyte as specified in 3.3.1 and shall be fully charged when shipped. When fully charged, the specific gravity of the electrolyte shall be  $1.280 \pm .010$ , corrected to electrolyte temperature of  $80^{\circ}\text{F}$  ( $27^{\circ}\text{C}$ ) and the open circuit, terminal-to-terminal voltage shall be not less than 2.10 V per cell corrected to  $80^{\circ}\text{F}$  ( $27^{\circ}\text{C}$ ).

3.7 Battery performance.

3.7.1 Cold activation of dry charge. Batteries furnished in the charged and dry condition shall exhibit a terminal voltage of 7.2 V or greater following the discharge rate and time specified on MS52149 after stabilizing the dry charged battery at  $30^{\circ} \pm 2^{\circ}\text{F}$  ( $-1^{\circ} \pm 1^{\circ}\text{C}$ ), and filling the battery with electrolyte also stabilized at the  $30^{\circ}\text{F}$  temperature (see 4.8.5).

3.7.2 Full charge capacity. Each battery shall yield a capacity of not less than that specified on MS52149 at a controlled temperature of  $80^{\circ} \pm 5^{\circ}\text{F}$  ( $27^{\circ} \pm 3^{\circ}\text{C}$ ) (See 4.8.12).

3.7.3 Reserve capacity. Fully charged batteries stabilized at  $80^{\circ} \pm 5^{\circ}\text{F}$  ( $27^{\circ} \pm 3^{\circ}\text{C}$ ) shall exhibit a minimum terminal voltage of 10.5 after a discharge rate of 25 amperes (A) for the time specified on MS52149 (see 4.8.13).

3.7.4 Low temperature capacity. Fully charged batteries (1.280 specific gravity, minimum) shall exhibit a minimum terminal voltage of 7.2 V after being discharged at the rate and time specified on MS52149 at temperatures of  $0^{\circ}\text{F}$  ( $-18^{\circ}\text{C}$ ) and  $-40^{\circ}\text{F}$  ( $-40^{\circ}\text{C}$ ) (see 4.8.14).



## MIL-B-62346C(AT)

3.7.5 Retention of charge. Following 30 days storage at 105 °F (40.6° C), batteries shall successfully survive a discharge rate of 25 A for the time specified on MS52149 to a minimum terminal voltage of 10.5 V (see 4.8.15).

3.7.6 Electrolyte retention. Batteries shall evidence no leakage or spillage when tilted through an angle of 45 degrees from the normal plane of either major or minor axis (see 4.8.16).

3.7.7 Extreme temperature resistance. Batteries shall show no cracking of containers, covers, sealer, filler plugs, or other damage due to temperature change between +190° F (88° C) and -65° F (-54° C) and no more than 0.1 psi pressure drop in 30 seconds, with 0.5 psi pressure applied to each cell individually after exposure to extreme test temperature (see 4.8.17).

3.7.8 Vibration resistance. Batteries shall maintain a steady voltage and current with no loosening of terminal posts in the cover; flooding of electrolyte at the top; intercell leakage; excessive sediment; broken connections, straps or plates; broken or defective separators; or other damage while being subjected to vibration through an amplitude of 0.045 to 0.050 inch (0.090 to 0.100 inch total excursion) at a frequency of 2,000 to 2,100 cycles per minute. Vibration shall not decrease the reserve capacity of batteries below that specified on MS52149 (see 4.8.18).

3.7.9 Life-cycle capacity. Battery shall withstand 235 discharge/charge cycles. The life-cycles attained by each battery shall be taken as the total actual cycles completed on life cycle tests, plus each cycle attained on other tests (see 4.8.19).

3.7.10 Storage life. After 90 days of storage at standard test conditions, the battery shall exhibit a terminal voltage of 7.2 V or greater following the discharge rate and time specified on MS52149, for storage life after 90 days (see 4.8.20).

3.8 Identification marking. Marking data shall be applied to a permanent, electrolyte-resistant type label or nameplate, or may be molded on battery container. Labels and nameplates shall be securely and permanently attached to the

MIL-B-62346C(AT)

side of the battery. A permanent label with removable tabs for identifying the "in-service" date (month and year) shall be provided on the battery top. It shall be optional to place the lot number on the battery top.

3.8.1 Identification data. Identification marking shall show the following:

- a. Battery identification (battery, storage, lead-acid, low maintenance).
- b. Designation (Military and SAE, when applicable).
- c. MS part number.
- d. Voltage.
- e. Reserve capacity at 80° F (26.7° C).
- f. High discharge capacity and rate at 0° F (-17.8° C) and -40° F (-40° C).
- g. Contract or order number.
- h. Date of manufacture (month and year) and lot number.
- i. Manufacturer's name.
- j. US

3.8.2 Instruction tag and label. Instruction tag and label which provide complete information for placing battery in service, operation, and charging shall be attached in a conspicuous place on each battery. The manufacturer's standard warning label regarding the hazards of acid and explosive gasses shall be permanently attached in a conspicuous place on each battery.

3.8.3 Instruction (charged and dry). Instructions for charged and dry batteries shall contain the following minimum information:

- a. NOTE: This is a CHARGED and DRY storage battery. When placing in service, identify the "in-service" date by removing the proper tabs from the permanent label.

## MIL-B-62346C(AT)

b. Remove and destroy sealing devices which seals cells during shipment and storage.

CAUTION: Do not remove sealing devices until ready to fill battery.

c. Fill each cell with electrolyte (sulfuric acid and water solution) of  $1.280 \pm .005$  specific gravity at  $80^{\circ} \text{ F}$  ( $26.7^{\circ} \text{ C}$ ) to designated level per instructions furnished by manufacturer. Temperature of the battery and the electrolyte must be above  $60^{\circ} \text{ F}$  ( $15.5^{\circ} \text{ C}$ ), but preferably not above  $100^{\circ} \text{ F}$  ( $37.8^{\circ} \text{ C}$ ).

d. Allow the battery to stand 30 minutes after filling, then check electrolyte specific gravity of each cell, correcting the reading to  $80^{\circ} \text{ F}$  ( $26.7^{\circ} \text{ C}$ ). Add electrolyte, if necessary, to bring to the designated level.

e. The battery shall be charged full at constant 15 volts before it is put into service using procedures specified in 4.5.2.

f. Charging current shall not exceed 6 amps. The temperature of the electrolyte during the charging period shall not be allowed to exceed  $120^{\circ} \text{ F}$  ( $48.9^{\circ} \text{ C}$ ).

g. Add electrolyte, as required, to bring to the proper level. Add only distilled water after initial charge to maintain proper level.

h. Keep the top and sides of the battery clean and dry. Make sure vent-filler plugs are clean. When cleaning is required, wash with water.

i. Battery should be charged every six months or when specific gravity of any cell falls below 1.250 and kept in cool, dry storage when not in use.

j. Electrolyte volume \_\_\_\_\_.

3.8.4 Instructions (charged and wet). Instructions for charged and wet batteries shall contain the following information:

## MIL-B-62346C(AT)

a. NOTE: This is a CHARGED and WET storage battery. It was activated at time of manufacture and charged to full rated capacity.

b. Indicate the date of preparation for service by removing the proper tabs from the permanent label.

c. Check the electrolyte specific gravity and levels in all cells, and adjust to the proper levels by adding distilled water as required. Charge at a constant voltage of 15 volts until the specific gravity of the electrolyte remains constant for three consecutive readings taken at 30 minute intervals.

d. Check the electrolyte levels. Add distilled water, as required, to maintain proper level. Add the water only while the battery is being charged.

e. The battery is now ready for use.

f. Keep the top and sides of the battery clean and dry. Make sure the vent filler plugs are clean. When cleaning is required, wash with water.

g. Battery should be charged every six months or when specific gravity of any cell falls below 1.250 and kept in cool, dry storage when not in use.

3.9 Workmanship. Batteries shall be processed in such a manner as to be uniform in quality and free of defects that will affect their life, serviceability, or appearance. Containers, covers, and vent filler plugs shall be free of cracks, leaks, and broken parts. Lead burning shall be homogeneous and free of blow holes or imperfect bonds between parts which have been burned together. Marking shall be clear and distinct.

#### 4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order (see 6.2), the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable

## MIL-B-62346C(AT)

for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform or witness any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items must meet all requirements of Sections 3 and 5. The inspection set forth in this specification shall become part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.2 Inspection of materials and components. All materials and battery components shall be inspected and tested by the contractor, before being assembled into batteries, to the extent necessary to insure that materials and components conform to this specification.

4.2.1 Contractor's inspection records. Contractor's inspection records shall be examined to determine conformance to 3.3, 3.3.1, and 3.3.2.

4.3 Classification of inspection: Inspections specified herein are classified as follows:

- a. Qualification inspection (4.6)
- b. In-process inspection (4.7)
- c. Quality conformance inspection (4.7.2)
- d. Special sampling inspection (4.7.4)
- e. Inspection of packaging (4.8.21)

4.4 Inspection conditions and equipment.

## MIL-B-62346C(AT)

4.4.1 Standard test conditions. Unless otherwise specified herein, all measurements and tests shall be made at a temperature between 68° F (20° C) and 95° F (35° C), and ambient atmospheric pressure and relative humidity.

4.4.2 Temperature of electrolyte. Unless otherwise specified herein, the temperature of the electrolyte at the beginning of the tests shall be within  $\pm 2^\circ$  F of the test temperature.

4.4.3 Test equipment. Test equipment shall be of sufficient accuracy and quality to permit performance of the required tests. The contractor shall establish adequate calibration of test equipment to the satisfaction of the Government. Precision measuring instruments shall conform to the requirements of MIL-STD-45662.

4.4.3.1 Hydrometer. The hydrometer shall provide a float accuracy of  $\pm 3$  points (.003) throughout the specific gravity scale and temperature range.

4.4.4 Instrument accuracy.

4.4.4.1 Electrical indicating instruments. All voltmeters and ammeters used in testing batteries shall be accurate within  $\pm 0.5$  percent of full scale value. The sensitivity of voltmeters shall be at least 20,000 ohms per volt. The voltmeter and ammeter ranges used shall be such that all readings are taken on the upper half of the scale.

4.4.4.2 Resistor tolerances. In all tests involving discharge through a resistance, such resistance shall be accurate within  $\pm 0.5$  percent.

4.5 Discharging and charging of test batteries.

4.5.1 Discharging. The fully charged battery shall be at a temperature of  $80^\circ \pm 5^\circ$  F ( $26.7^\circ \pm 3^\circ$  C) and shall be discharged at the 20 hour rate (that current in amperes equal to 1/20th of the battery's rated ampere hour capacity), to a final average terminal voltage equivalent to 1.75 volts per cell, unless otherwise specified.

## MIL-B-62346C(AT)

4.5.2 Charging. Batteries shall be charged at a constant voltage of 15.0 volts until specific gravity reading taken at 30 minute intervals remains constant. Charging current shall not exceed six amperes. The temperature of the electrolyte during the charging period shall not be allowed to exceed 120 ° F (48.9 ° C). Optional: Batteries shall be charged as specified in SAE Standard J537.

4.5.3 Periodic charging. If the testing on any activated battery is temporarily stopped for a period of 48 hours, the battery shall be given a freshening charge at the specified rate until fully charged (see 4.5.2) before testing is resumed. A battery shall never be stored for more than 24 hours after a discharge, without being recharged.

4.6 Qualification. Qualification inspection shall be conducted at a place designated by, or approved by, the Government. Qualification inspection shall consist of examination of defects listed in Table IV and tests listed in Table III (see 3.2).

TABLE II. Qualification samples.

<u>Sample description</u>	<u>Quantity required</u>
Batteries, complete	8 each
Container	3 each
Covers	3 each
Vent filler plugs	1 set (six each)

## MIL-B-62346C(AT)

TABLE III. Order of QPL inspection.

<u>Description</u>	<u>Sample 1/ Number</u>	<u>Requirement</u>	<u>Test</u>
Electrical breakdown	CT1	3.5.1	4.8.1
Acid absorption	CT1/CV1	3.5.2	4.8.2
Impact resistance	CT2	3.5.3	4.8.3
Bulge resistance	CT3	3.5.4	4.8.4
Cold activation dry charged batteries	B2-6	3.7.1	4.8.5
Covers	CV2	3.4.2	4.8.6
Vent filler plugs	V1-6	3.5.8	4.8.7
Handles	B1	3.5.9	4.8.8
Terminal post torque resistance	B7	3.5.13.1	4.8.9
Moisture content dry charged batteries	B7	3.6.1	4.8.10
Dry cell internal resistance	B7	3.6.1.1	4.8.11
Full charge capacity	B4/5	3.7.2	4.8.12
Reserve capacity	B2-6	3.7.3	4.8.13
Low temperature capacity	B2-6	3.7.4	4.8.14
Retention of charge	B6	3.7.5	4.8.15
Vent plug flame retardancy	B6	3.5.8	4.8.7.1
Electrolyte retention	B2/3	3.7.6	4.8.16
Extreme temperature	B2/3	3.7.7	4.8.17
Vibration	B2/3	3.7.8	4.8.18
Life cycle capacity	B4/5	3.7.9	4.8.19
Storage life	B8	3.7.10	4.8.20

1/ B = Battery sample  
 CT = Container sample  
 CV = Cover sample  
 V = Vent plug sample set (six)



## MIL-B-62346C(AT)

4.6.1 Failure. Failure of a qualification sample to conform to any of the requirements specified, or any deficiency of a workmanship or material nature found as a result of the test, shall be cause for rejection. Further testing shall not be conducted until evidence has been provided by the contractor that corrective action has been taken to eliminate the deficiency.

4.7 In-Process inspection. Before and during assembly, as applicable, grids and plates, plate connections and internal connector, separators and protectors, and completed assembly shall be examined and measured to determine conformance to 3.5.10, 3.5.11, 3.5.12, and 3.6.1.1.

4.7.1 Lot formation. An inspection lot shall consist of a quantity of batteries of any one part number, from an identifiable production period, from one manufacturer, submitted at one time for acceptance.

4.7.1.1 Sampling for examination. Samples for quality conformance examination shall be selected at the rate of four fully completed batteries per each production lot. When production lots exceed 5,000 per week, four additional test samples shall be selected and tested.

4.7.2 Quality Conformation Examination

4.7.2.1 Classification of defects. For examination purposes, defects shall be classified as listed in Table IV.

4.7.3 Pressure test. Each cell of samples selected for testing shall be subjected to 0.5 psi (3.45 KPa) using dry air or nitrogen gas for a period of 30 seconds. A drop in pressure of 0.10 psi (0.69 KPa) in any cell shall be considered a failure of the sample battery.

4.7.3.1 Quality conformance examination failure. Failure of the test samples shall require retest per paragraph 4.7.4.2.

4.7.4 Special sampling inspection. Samples shall be selected at the rate of four fully completed batteries per each production lot. One battery shall be tested as shown in Table V for each group. Samples shall be examined for the defects specified in 4.7.2.1. When production lots exceed 5,000 per week, four additional test samples shall be selected and tested.

## MIL-B-62346C (AT)

TABLE IV. Classification of defects.

<u>Category</u>	<u>Defect</u>	<u>Method of examination</u>
Non-Critical		
<u>Major</u>		
101	Maximum dimensional limitations exceeded (see 3.4, 3.4.1, and 3.4.2)	Scale
102	Location and polarity of terminal posts not as specified (see 3.5.13)	Visual
103	Loose terminal posts	Manual
104	Terminal markings not as specified (see 3.5.13)	Visual
105	Dimensions of terminal posts not as specified (see 3.5.13)	Scale
106	Low electrolyte level (charged and wet batteries only (see 3.6.2)	Visual
107	Specific gravity of electrolyte out of limits (charged and wet batteries only) (see 3.6.2)	Hydrometer
108	Open circuit, terminal-to-terminal voltage, less than 2.10 volts per cell (charged and wet batteries only) (see 3.6.2)	Voltmeter
109	Vent holes not properly sealed (charged and dry batteries only) (see 3.5.7)	Visual
110	Vent filler plugs and filler caps not as specified (see 3.5.8)	Visual and 4.8.7.1
111	Post seals not as specified (see 3.5.6)	Visual
112	Leaks or cracks in container (see 3.4.1)	4.7.3
113	Cover not properly sealed to container (see 3.4.2)	Visual
114	Vent openings in cover not as specified (see 3.5.5)	Visual/ Scale
115	Electrolyte level instructions not as specified (see 3.8.3)	Visual
116	Missing or improper instructions (see 3.8.2)	Visual
<u>Minor</u>		
201	Improper marking (see 3.8.1)	Visual
202	Handles not as specified (see 3.5.9)	Visual
203	Workmanship defects (see 3.9)	Visual

## MIL-B-62346C (AT)

TABLE V. Order of Special Sampling Inspection.

	DESCRIPTION	REQUIREMENT	TEST
I.	<u>Group A Tests</u>		
	a. Handles test (80 F only)	3.5.9	4.8.8
	b. Cold activation	3.7.1	4.8.5
	c. Reserve capacity	3.7.3	4.8.13
	d. Terminal post torque	3.5.13.1	4.8.9
II.	<u>Group B Tests</u>		
	a. Cold activation	3.7.1	4.8.5
	b. Low temperature capacity	3.7.4	4.8.14
III.	<u>Group C Tests</u>		
	Extreme temperature resistance	3.7.7	4.8.17
IV.	<u>Group D Tests</u>		
	a. Reserve capacity	3.7.3	4.8.13
	b. Vibration	3.7.8	4.8.18

4.7.4.1 Group A test failure. Failure of Group A handles test sample shall require retest of Group A handles test sample to all requirements of 3.5.9 and 4.8.8.

4.7.4.2 Special sampling test failures. Failure of a sample to pass any of the tests outlined in Table V, Special Sampling Inspection, shall require resample and retest per 4.7.4.2.1 through 4.7.4.2.4.

## MIL-B-62346C(AT)

4.7.4.2.1 Samples from production lots, which failed the initial test, shall be selected at the rate of two batteries (per each day represented in the lot).

4.7.4.2.2 Retest samples shall be subjected to only the tests related to mode of failure.

4.7.4.2.3 Any production lots, which fail the resampling test, may be further divided into operator or shift, sub-lots, and retested.

4.7.4.2.4 Two retest failures of a sub-lot may be cause for rejection, by the Government, of the lot or lots represented by those samples.

#### 4.8 Conformance verification.

4.8.1 Electrical breakdown test for containers. The battery container shall be filled with lead or aluminum shot or fitted with a close fitting mandrel or other electrode to within 1/2 inch of the top of the lowest point on the sides, ends, or partitions of the containers. An alternating current potential of 100 V rms per mil of thickness shall be applied for 15 seconds after full calculated voltage has been reached. Voltage shall be supplied by a transformer of not less than 1/2 kilovoltampere capacity, using the electrodes in a manner that will subject each outer wall and inner partition of the container to the electrode potential. Containers shall subsequently be examined for leaks, imperfections, or other evidence of perforation or burn-through to determine conformance to 3.5.1.

4.8.2 Acid absorption test for containers. Two specimens, each 3 by 3 inches, shall be cut from the partitions of the container. After being measured with calipers and weighed in the dry condition at plus  $80^{\circ} \pm 10^{\circ}$  F ( $26.7^{\circ} \pm 6^{\circ}$  C), each specimen shall be immersed in a covered vessel containing 150 cubic centimeters (cc) of sulfuric acid solution of 1.300 specific gravity at  $80^{\circ}$  F ( $26.7^{\circ}$  C). The vessel shall be held for seven days in an oven at  $150^{\circ} \pm 5^{\circ}$  F ( $65.6^{\circ}$  C  $\pm 3^{\circ}$  C). At the end of the heating period, the specimens shall be inspected for evidence

## MIL-B-62346C(AT)

of cracks or blisters and then measured and weighed. The percentage increase in dimensions and weight shall be calculated to determine conformance to 3.5.2.

4.8.3 Impact resistance test. An undamaged specimen container shall be permitted to rest not less than 24 hours after manufacture. Before testing, the sample shall be conditioned for four hours at each test temperature. The test shall be conducted in an  $150^{\circ} \pm 5^{\circ}$  F ( $65.6^{\circ} \pm 2.8^{\circ}$  C),  $0 \pm 2^{\circ}$  F ( $-17.8^{\circ}$  C) and  $-40^{\circ}$  F ( $-40^{\circ}$  C) atmosphere. Impact resistance shall be determined by a two pound solid steel ball, used as free falling weight. When testing, the height of drop necessary to crack the container on the inside opposite the point of impact is the impact value for that section. The impact resistance shall be found by dropping the weight at the height necessary to produce the minimum impact resistance requirement for the test temperature (see Table I). The weight shall hit the container only once for each drop. During the test, the container shall be positioned on a flat steel plate, about an inch longer and wider than the container. The container shall be positioned in such a manner that the ball will strike 1/3 down from the top of the container on the centerline of the sides of each cell and on the center of each cell cover area (where thickness is uniform). Testing of post cells is not required (see 3.5.3).

4.8.4 Bulge resistance. The bulge resistance of the battery container shall be determined as follows:

- a. Place an empty container, to be tested, in an appropriate rigid metal tray.
- b. Fill the container to within 25 mm (one inch) of the top with commercial grade polyethelene glycol at a temperature of  $93^{\circ}$  C  $\pm$   $3^{\circ}$  C ( $200^{\circ}$   $\pm$   $5^{\circ}$  F).
- c. Place the tray, containing the container, to be tested, in an oven and maintain the polyethylene glycol at  $93^{\circ}$  C  $\pm$   $3^{\circ}$  C ( $200^{\circ}$   $\pm$   $5^{\circ}$  F).
- d. When the liquid in the end cell adjacent to the end wall, to be measured, reaches a temperature of  $93^{\circ}$  C  $\pm$   $3^{\circ}$  C ( $200^{\circ}$   $\pm$   $5^{\circ}$  F) start a one hour soak time.

## MIL-B-62346C(AT)

e. At the end of the soak period, remove the tray containing the container being tested, from the oven and within five minutes, measure the end wall bulge, using the spider arrangement. The polyethylene glycol is to remain in the test container until the completion of the measurements.

f. The bulge shall be determined by comparing the center of the end wall with the plane of the four corners exposed. The center of the end wall is defined as a point half way between the horizontal parting line at the bottom and the bottom of the top band.

g. Bulge is to be reported as the difference as determined in subparagraph f.

The bulges in the container shall be measured to determine conformance to 3.5.4.

4.8.5 Cold activation. This test shall apply to batteries furnished in charged and dry condition and without supplementary charge. The battery and electrolyte,  $1.280 \pm .005$  specific gravity at  $80^\circ \text{ F}$  ( $26.7^\circ \text{ C}$ ) shall be placed in a cold chamber at  $30^\circ \pm 2^\circ \text{ F}$  ( $-1^\circ \pm 1^\circ \text{ C}$ ) for at least 18 hours prior to test and held until both battery and acid are at  $30^\circ \pm 2^\circ \text{ F}$  ( $-1^\circ \pm 1^\circ \text{ C}$ ). The electrolyte shall conform to 3.3.1. Remove from cold chamber and immediately fill the battery with the cold electrolyte. Allow battery to stand 30 minutes after filling last cell. Record gravity and temperature of the electrolyte. Discharge the battery at 450 amperes. Note and record the terminal voltage at 60 seconds to determine conformance to 3.7.1.

4.8.6 Battery cover physical characteristics. Battery covers shall be tested as specified in 4.8.1, 4.8.2 and 4.8.3 with appropriate modifications in samples and procedures. Results shall be evaluated as specified in referenced paragraphs to determine conformance to 3.4.2.

4.8.7 Vent filler plug thermal and pressure resistance test. To determine conformance to 3.5.8, each vent filler plug from the battery under test shall be placed in an ambient air temperature of  $-65^\circ \pm 2^\circ \text{ F}$  ( $-54^\circ \pm 1^\circ \text{ C}$ ) for two hours. At the end the cooling period, the plugs shall be


## MIL-B-62346C(AT)

removed and immediately placed in an oven at an ambient air temperature of  $+ 250^{\circ} \pm 5^{\circ} \text{ F}$  ( $121^{\circ} \pm 3^{\circ} \text{ C}$ ) for 90 minutes. The plugs shall then be removed and inspected for evidence of damage such as cracking or melting. After a cooling period of one hour, each vent filler plug shall be inserted in a fixture arranged so that water pressure can be applied on the upper side of the plug, and air pressure on the lower side. Using this fixture, the upper side of each plug shall be subjected to a water pressure which exceeds the air pressure on the lower side by 1.75 psi (water head of four feet, if air pressure is atmospheric). The number of drops of water that leaks through each vent filler plug and the time required therefore (not to be less than one minute) shall be recorded. The water pressure shall then be released and the air pressure on the lower side increased to 0.5 psi above the pressure existing on the upper side. Plug shall open under specified pressure.

4.8.7.1 Vent plug flame retardancy test. Battery and vent plugs shall be tested for flame retardancy per SAE J1495.

4.8.8 Handle test. The handle and bond areas shall be saturated with electrolyte conforming to 3.3.1 and air dried twice daily for two days. The handles and bond areas shall again be saturated. The battery shall then be placed in an ambient air temperature of  $\text{plus } 190^{\circ} \pm 2^{\circ} \text{ F}$  ( $88^{\circ} \pm 1^{\circ} \text{ C}$ ) for 60 minutes, allowed to cool to room temperature, and again heated at  $190^{\circ} \pm 2^{\circ} \text{ F}$  ( $88^{\circ} \pm 1^{\circ} \text{ C}$ ) for 60 minutes. The battery shall then be removed from the oven and immediately placed in a test fixture similar to Figure 1. The battery shall be initially set on the removable support, and the angles and initial tautness of the handles shall be set with the support in place. The ballast weight, equal to the dry weight of the test battery, shall be placed on top of the test battery (a second similar battery may be used). The support shall then be slowly removed and the battery and weight be allowed to hang freely by the handles for 60 seconds. The battery shall then be removed and the handles and bond shall be examined for conformance to 3.5.9. After the test, the battery shall be placed in an ambient air temperature of  $\text{minus } 65^{\circ} \pm 2^{\circ} \text{ F}$  ( $-54^{\circ} \pm 1^{\circ} \text{ C}$ ) for 24 hours. The battery shall be removed from the cold box and immediately subjected to the handle test previously specified. At the conclusion of the test, the handles and bond shall be examined for conformance to 3.5.9.

MIL-B-62346C (AT)

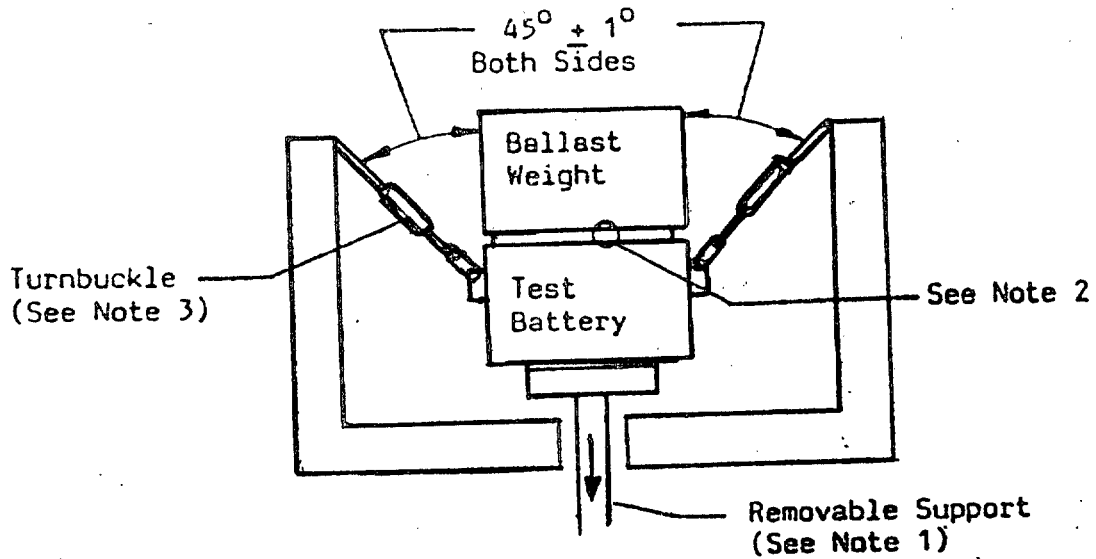

- NOTES:
1. Support shall allow gradual and even removal so as to minimize shock and insure even loading of both handles.
  2. A lightweight (less than 2 lbs or 1 kg) shim may be used between battery and weight to prevent damage to caps, posts or cover.
  3. Turnbuckles shall be used to establish 45 angle of handles with test weight applied after removal of support. Turnbuckles shall include a device to support rope handles over a length of 4-1/2 inches (114 mm) during test.

FIGURE 1. Handle test.



## MIL-B-62346C (AT)

4.8.9 Terminal post torque resistance. An increasing torque up to 250 pound-inches shall be applied in a direction perpendicular to the axis of the terminal posts and parallel to the top of the battery by a torque-indicating device, through a fitted battery terminal or other clamping device. Observation shall be made for evidence of distortion of the strap and connected plates, or of the seal between the posts and the cell cover. If no evidence of distortion or visible damage to post seal is revealed, the leakage test in 4.7.3 shall be made to determine conformance to 3.5.13.1.

4.8.10 Charged and dry moisture. To determine moisture content (see 3.6.1), the plates and separators shall be weighed. They shall be dried in an oven at atmospheric pressure and a temperature of 165° to 170° F (73.9° to 76.7° C) to 2 hours, or to a constant weight. The plates and separators shall be reweighed and the percentage of moisture computed.

4.8.11 Individual cell dry internal resistance test. The cell terminal-to-terminal resistance shall be measured with an ohmmeter, bridge, or other test instrument to determine conformance to 3.6.1.1.

4.8.12 Full charge capacity test at 80 F (26.7 C). The battery full charge capacity rating (ampere-hours) shall be determined as follows to determine conformance to 3.7.2:

a. Charge battery before each discharge in accordance with 4.5.2.

b. The temperature of the battery at the beginning of each discharge shall be  $80^{\circ} \pm 5^{\circ} \text{ F}$  ( $26.7^{\circ} \pm 3^{\circ} \text{ C}$ ), and the temperature shall be maintained within this range by means of a water bath, or controlled air temperature condition, during discharge.

c. Discharge battery in accordance with 4.5.1, record the discharge time, and calculate the ampere-hour capacity.

d. Repeat steps a, b, and c.

e. Repeat steps a, b, and c.

## MIL-B-62346C(AT)

f. The ampere-hour capacity obtained from each battery subjected to steps c, d, and e shall represent the full charge capacity. Exception: If the ampere-hour capacity is met in steps c or d, extra steps are not required.

4.8.13 Reserve capacity test. Reserve capacity tests shall be conducted as follows to determine conformance to 3.7.3:

a. Charge battery before each discharge in accordance with 4.5.2.

b. The temperature of the battery at the beginning of each discharge shall be  $80^{\circ} \pm 5^{\circ}$  ( $26.7^{\circ} \pm 3^{\circ}$  C), and the temperature shall be maintained within this range by means of a water bath, or controlled air temperature condition, during discharge.

c. Discharge battery at  $25 \pm 0.25$  amperes to a terminal voltage of 10.5 volts. Record the time of discharge in minutes.

d. Repeat steps a, b, and c.

e. Repeat steps a, b, and c.

f. The longest time of discharge obtained from each battery subjected to steps c, d, and e shall represent the reserve capacity of the battery. Exception: If the reserve capacity requirement is met in steps c or d, remaining steps through step e are not required.

The following correction factor shall be used to compensate for electrolyte temperature variation from the stabilized  $80^{\circ} \pm 5^{\circ}$  F ( $26.7^{\circ} \pm 3^{\circ}$  C).

Mc	=	Mr (1 - 0.005 (Tf - 80))
Mc	=	Corrected minutes
Mr	=	Minutes run
Tf	=	Temperature at one end of discharge
0.005	=	Temperature correction factor

1/ Results not valid if electrolyte temperature is above  $90^{\circ}$  F ( $32.3^{\circ}$  C) or below  $70^{\circ}$  F ( $21^{\circ}$  C) at completion of test.

## MIL-B-62346C(AT)

4.8.14 Low temperature capacity test. The test for high discharge rate at  $0^{\circ}\text{F}$  ( $-17.8^{\circ}\text{C}$ ) and minus  $40^{\circ}\text{F}$  ( $-40^{\circ}\text{C}$ ) shall be performed as follows to determine conformance to 3.7.4:

- a. Charge battery in accordance with 4.5.2.
- b. Place battery in cold chamber having a temperature of minus  $40^{\circ} \pm 5^{\circ}\text{F}$ .
- c. When the electrolyte has stabilized for one hour at minus  $40^{\circ} \pm 5^{\circ}\text{F}$  and immediately upon removal from the cold chamber, the battery shall be discharged at the rate and time specified on MS52149.
- d. At this time the voltage shall be measured to determine conformance to 3.7.4.
- e. If a battery fails the test, it shall be retested. The retested battery shall be charged, discharged, and charged in accordance with 4.5.2 with electrolyte stabilized at  $80^{\circ} \pm 5^{\circ}\text{F}$  ( $26.7^{\circ} \pm 3^{\circ}\text{C}$ ), and then retested as specified in steps a through d. Failure of a battery to pass this second cycle shall be considered as failure to meet the specified requirement.
- f. Test as per 4.8.13.
- g. Repeat steps a through e, except temperature shall be  $0^{\circ}\text{F} \pm 1^{\circ}\text{F}$  ( $-17.8^{\circ} \pm 1^{\circ}\text{C}$ ) and discharge rate shall be at the rate and time specified on MS52149.

4.8.15 Retention of charge test. The retention of charge test shall be performed as follows:

- a. Charge battery as specified in 4.5.2. Store battery for 30 days at a temperature maintained at  $105^{\circ} \pm 5^{\circ}\text{F}$  ( $40.6^{\circ} \pm 3^{\circ}\text{C}$ ).
- b. Discharge battery as specified in 4.8.13.c.
- c. Record time of discharge in minutes to determine conformance to 3.7.5.

## MIL-B-62346C(AT)

4.8.16 Electrolyte retention test. Batteries shall be tilted through 45 degrees from a plane normal to the bottom of the battery along the major axis, held along the minor axis. Batteries shall be observed for evidence of leakage, or spillage of electrolyte, to determine conformance to 3.7.6.

4.8.17 Extreme temperature resistance test. Batteries shall be subjected to two thermal shock cycles to determine conformance to 3.7.7. An internal pressure of 0.5 psi shall be applied to each cell individually in parallel with a manometer at  $80^{\circ} \pm 5^{\circ} \text{ F}$  ( $26.7^{\circ} \pm 3^{\circ} \text{ C}$ ) for 30 seconds before and after each complete cycle. Drop in pressure in the individual cells shall be regarded as an indication of leakage (see 3.7.7). The following procedure for one cycle shall be used:

a. Battery shall be placed in an ambient air temperature of  $\text{minus } 65^{\circ} \pm 2^{\circ} \text{ F}$  ( $-54^{\circ} \pm 1^{\circ} \text{ C}$ ) for 24 hours, or until electrolyte is stabilized.

b. The battery shall be then placed in an ambient air temperature of  $190^{\circ} \pm 2^{\circ} \text{ F}$  ( $87.8^{\circ} \pm 1^{\circ} \text{ C}$ ) for 24 hours.

c. The battery shall be allowed to cool gradually to  $80^{\circ} \pm 10^{\circ} \text{ F}$  ( $26.7^{\circ} \pm 6^{\circ} \text{ C}$ ) for 24 hours.

4.8.18 Vibration resistance test. The test specimen shall be stabilized, then subjected to 4.8.13 a, b, and c in an ambient air temperature of  $80^{\circ} \pm 10^{\circ} \text{ F}$  ( $26.7^{\circ} \pm 6^{\circ} \text{ C}$ ) prior to vibration. Apparatus shall include a hold down frame to bear on the top edges of the battery container, but not on the vent plugs or terminal posts. While in an ambient air temperature of  $80^{\circ} \pm 10^{\circ} \text{ F}$  ( $26.7^{\circ} \pm 6^{\circ} \text{ C}$ ) and mounted in the vibrating machine, the specimen shall be vibrated for two hours at a frequency of 2,000 to 2,100 cycles per minute through an amplitude of 0.045 to 0.050 inch (total excursion 0.090 to 0.100 inch). During this test the battery shall be discharged at the 20 hours rate. The test shall be repeated for one hour, except that the battery shall be chilled to, and the electrolyte stabilized at a temperature of  $\text{minus } 40^{\circ} \pm 2^{\circ} \text{ C}$  for one hour immediately before beginning vibration. During the test, the battery shall be observed for maintenance of steady voltage and current, and thereafter

## MIL-B-62346C(AT)

examined for evidence of loosening of terminal posts in the covers and flooding of electrolyte at the top. The battery shall be removed from the vibrating machine, allowed to warm to  $80^{\circ} \pm 10^{\circ} \text{ F}$  ( $26.7^{\circ} \pm 6^{\circ} \text{ C}$ ) until the electrolyte is stabilized, the subjected to 4.8.13 a, b, and c. The battery shall conform to 3.7.8.

4.8.19 Life-cycle capacity tests. Life tests shall consist of a series of discharge and charge in accordance with the applicable test specified in 4.8.19.1. Immediately prior to the beginning of the test, the battery shall be fully charged as specified in 4.5.2. Tests shall be performed with the battery in a water bath with the temperature maintained at  $100^{\circ} \pm 5^{\circ} \text{ F}$  ( $37.8^{\circ} \pm 3^{\circ} \text{ C}$ ). Water shall be added as required to each cell to replace evaporation (except during the capacity discharge test cycle for ampere-hour capacity). When the ampere-hour capacity equals or drops below 40 percent of the rated ampere-hour capacity during the capacity discharge test cycle, the battery shall be full charged as specified in 4.5.2 and tested as specified in 4.8.12. If the capacity is above 40 percent of normal full charged value, the life test shall be continued. If the capacity equals or falls below 40 percent, the life cycle test shall be terminated. The life cycle attained by a battery shall be taken as the total of the actual cycles completed on the life test, plus each cycle received on other tests (see 3.7.9).

4.8.19.1 Life-capacity discharge cycles. To determine conformance to 3.7.9, the test shall consist of a total of 235 discharge/charge cycles including normal and weekly cycles and cycles attained on other tests:

a. Normal cycles. The normal cycles shall consist of a series of six hour cycles (four cycles per day or approximately 24 per week). Each cycle shall consist of discharge for one hour at 40 amperes and charge for five hours at 10 amperes.

b. Weekly capacity discharge cycles. Ampere hour capacity shall be determined at the completion of each series of 24 normal cycles. The battery shall be discharged at the ampere rate for normal cycles, until a final average terminal

## MIL-B-62346C(AT)

voltage of 1.75 volts per cell has been reached. The ampere hour capacity shall be calculated as the product of the current rate in amperes and the time of discharge in hours. Following this discharge, the battery shall be fully charged per paragraph 4.5.2 or SAE J537 and the normal cycle procedure shall be continued. The battery shall be placed on a discharge cycle which, with the charge cycle, shall constitute a full normal cycle.

4.8.20 Storage life test. Specimens shall be stored under standard test conditions (see 4.4.1) for 90 days. After storage, the battery shall be tested per 4.8.5 to determine conformance to 3.7.10.

4.8.21 Inspection of packaging. Packaging inspection shall be accomplished in accordance with the quality assurance provisions of MIL-B-208, or the applicable packaging data sheet as selected from paragraph 5.1.1 (see 6.2).

## 5. PACKAGING

### 5.1 Dry and wet charged batteries.

5.1.1 Preservation, packaging, and packing. Charged wet and dry batteries shall be cleaned, dried, preserved, packaged, and packed to the desired level of protection in accordance with MIL-B-208 or the applicable packaging sheet as specified (see 6.2).

5.1.2 Marking. Marking shall be in accordance with MIL-STD-129, including lot numbers, except for any special marking requirements (see 6.2).

5.1.3 Transportation (charged and wet batteries). Charged and wet batteries shall be packaged and transported in conformance to DOT Regulation 49 CFR.

## 6. NOTES

6.1 Intended use. Batteries covered by this specification are intended primarily for starting, lighting, and ignition service in military vehicles, including tactical

## MIL-B-62346C(AT)

and administrative vehicles, internal combustion engine driven industrial trucks and tractors, and construction equipment and generator sets. The batteries will also be used for radio operation and as a source of electrical energy for operating vehicular accessories, such as sighting devices and control mechanisms.

6.2 Ordering data. Acquisition documents should specify the following:

- a. Title, number and date of this specification.
- b. Battery condition (see 3.6).
- c. Any special marking requirements (see 5.1.1).
- d. Level of preservation, packaging, and packing in accordance with MIL-B-208 or the applicable packaging data sheet (see 5.1.1).

6.3 Qualification. Qualification samples shall be tested and approved under the appropriate provisions of 7-104.55 of the Defense Acquisition Regulation. The contracting officer should include specific instructions in all procurement instruments regarding arrangements for all procurement instruments regarding arrangements for examination, tests and approval of the qualification (see 3.2).

6.4 Subject term (key word) listing.

Batteries  
Storage Batteries  
Lead-Acid Batteries

6.5 Definitions.

6.5.1 Recovered materials. "Recovered materials" means materials that have been collected or recovered from solid waste (see 6.5.2).

6.5.2 Solid waste. "Solid waste" means (a) any garbage, refuse, or sludge from a waste treatment plant, water supply treatment plant, or air pollution control facility; and (b)

MIL-B-62346C(AT)

other discarded material, including solid, liquid, semi-solid, or contained gaseous material resulting from industrial, commercial, mining, and agricultural operations, and from community activities. It does not include solid or dissolved material in domestic sewage, or solid or dissolved material in irrigation return flows or industrial discharges which are point sources subject to permits under Section 402 of the Clean Water Act (33 U.S.C. 1342 et seq.), or source, special nuclear, or by-product material as defined by the Atomic Energy Act of 1954 (42 U.S.C. 2011 et seq.) (Source: Federal Acquisition Regulations, Section 23.402).

Custodian:

Army - AT

Preparing activity:

Army - AT

(Project 6140-A629)