

NOT MEASUREMENT SENSITIVE

MIL-DTL-81736A(AS)

25 August 2006

SUPERSEDING

MIL-T-81736(AS)

14 August 1969

DETAIL SPECIFICATION

TAPE, TEXTILE, NYLON, LANDBASED ARRESTING GEAR, 8-INCH

This specification is approved for use by the Naval Air Systems Command and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers an 8-inch nylon tape having a breaking strength of not less than 150,000 pounds for use on landbased arresting gear.

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications and standards. The following specifications and standards form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

Comments, suggestions, or questions on this document should be addressed to: Commander, Naval Air Warfare Center Aircraft Division, Code 491000B120-3, Highway 547, Lakehurst, NJ 08733-5100 or emailed to thomas.omara@navy.mil . Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at http://assist.daps.dla.mil .

MIL-DTL-81736A(AS)

DEPARTMENT OF DEFENSE SPECIFICATIONS

- MIL-PRF-131 - Barrier Materials, Watervaporproof, Greaseproof, Flexible, Heat-Sealable
- MIL-W-27265 - Webbing, Textile, Woven Nylon Impregnated

DEPARTMENT OF DEFENSE STANDARDS

- MIL-STD-129 - Marking for Shipment and Storage
- MIL-STD-1480 - Color Codes for Webbing, Textile; Manufacturers' Identification

(Copies of these documents are available online at <http://assist.daps.dla.mil/quicksearch/> or <http://assist.daps.dla.mil> or from the Standardization Document Order Desk, 700 Robbins Avenue, Building 4D, Philadelphia, PA 19111-5094.)

2.2.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

NAVAL AIR SYSTEMS COMMAND

NAVAL AIR ENGINEERING CENTER (NAEC) DRAWINGS

- NAEC Drawing 506733 - Purchase Tape Assembly
- NAEC Drawing 510534 - Purchase Tape Assembly
- NAEC Drawing 613516 - Purchase Tape Assembly
- NAEC Drawing 508306 - Reel, Tape Assembly

(Copies of these documents are available from the Commander, Naval Air Warfare Center Aircraft Division, Code 4.8, Highway 547, Lakehurst, NJ 08733.)

CODE OF FEDERAL REGULATIONS

FEDERAL TRADE COMMISSION (FTC)

- 16 CFR Part 303 - Rules and Regulations under the Textile Fiber Products Identification Act

(Copies of these documents are available online at [http:// www.ftc.gov](http://www.ftc.gov) from the Federal Trade Commission, 600 Pennsylvania Avenue, Washington, DC 20580.)

MIL-DTL-81736A(AS)

2.3 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

AMERICAN ASSOCIATION OF TEXTILE CHEMISTS AND COLORISTS (AATCC)

AATCC-61 - Colorfastness to Laundering, Home and Commercial; Accelerated.

(Copies of these documents are available from www.aatcc.org or AATCC, PO Box 12215, Research Triangle Park, NC 27709-2215.)

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM) INTERNATIONAL

ASTM-D276 - Identification of Fibers in Textiles, Standard Test Method for. (DoD adopted)
ASTM-D1423 - Twist in Yarns by the Direct-Counting Method, Standard Test Method for. (DoD adopted)
ASTM-D1777 - Thickness of Textile Materials, Standard Test Method for.
ASTM-D1907 - Linear Density of Yarn (Yarn Number) by the Skein Method, Standard Test Method for. (DoD adopted)
ASTM-D3773 - Length of Woven Fabric, Standard Test Method for (DoD adopted)
ASTM-D3774 - Width of Textile Fabric, Standard Test Method for (DoD adopted)
ASTM-D3775 - Fabric Count of Woven Fabric, Standard Test Method for. (DoD adopted)
ASTM-D3776 - Mass Per Unit Area (Weight) of Fabric, Standard Test Method for. (DoD adopted)

(Copies of these documents are available from www.astm.org or ASTM International, 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959.)

2.4 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.


MIL-DTL-81736A(AS)

3. REQUIREMENTS

3.1 Materials.

3.1.1 Yarn. The yarn used in the manufacture of the tape shall have a tenacity of 8.5 grams per denier minimum, bright high tenacity, light and heat resistant nylon yarn. It shall be polyamide prepared from hexamethylene diamine and adipic acid, or its derivatives, and shall have a minimum melting point of 244 °C. The yarn shall be free from sizing, loading, or other adulterants, and shall not be bleached in any manner or by any process.

3.2 Weave. The weave shall be as shown on figure 1.

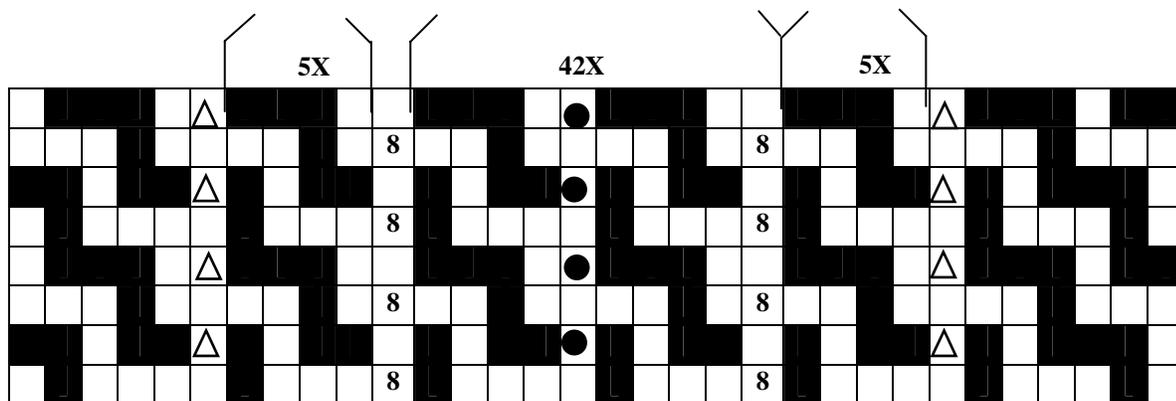KEY TO MARKS:

	STUFFER 36 ENDS		BODY	
	STUFFER 28 ENDS		BINDER	2 AS 1

FIGURE 1. Weave configuration.

3.3 Color. The color of the as woven tape shall be the natural color of the nylon yarn and uniform throughout the tape. The tape color after resin treatment (see 3.8) shall be black.

3.4 Construction and physical properties. The nylon tape shall conform to the construction and physical properties in table I.

MIL-DTL-81736A(AS)

TABLE I. Physical properties.

CHARACTERISTIC	REQUIREMENT	CONDITION
Width, inches	8.0 ± 0.062	resin treated
Thickness, inches	0.344 + 0.005 0.344 - 0.010	resin treated
Weight, ounces/yard (max)	50.0	resin treated
Breaking strength, pounds (min)	150,000 <u>1/</u>	as woven
Stiffness, pounds for one inch deflection:	75 + 20 75 - 10	as woven
Ends in warp (min)		as woven
Ground	387	
Binder	86	
Stuffer	1568	
Filling, yarns per inch (min)	13	as woven
Yarn size and ply, denier (min)		as woven
Ground		
840	6	
1260 (alternate)	4	
2520 (alternate)	2	
Binder		
840	5	
Stuffer		
840	6	
1260 (alternate)	4	
2520 (alternate)	2	
Filling		
840	8	
Ply twist, turns per inch		as woven
Ground	0.5 - 1.5	
Binder	1.0 - 2.0	
Stuffer	0.5 - 1.5	
Filling	0.5 - 1.5	

1/ A failure at or above 150,000 pounds tension or a jawbreak at or above 150,000 pounds shall be considered acceptable. A failure below 150,000 pounds tension or a jawbreak below 150,000 pounds shall be considered unacceptable.



3.5 Tape roll.

3.5.1 Length of roll. Unless otherwise specified in the contract or order, the length of each production tape roll shall be as specified in NAEC Drawing 613516, 506733, or 510534, as applicable (see 6.2).

MIL-DTL-81736A(AS)

3.5.2 Tape installation on reel. The tape shall be installed on a reel as shown on the applicable NAEC Drawing 506733, 613516, or 510534.

3.5.2.1 Tape installation procedure. When installing tape on reel, it shall be installed over barrier material conforming to MIL-B-131, class 1 which has been wrapped around the periphery of the reel hub. The barrier material shall also cover the sides of the tape reel (inside of the shipping reel) with two additional feet of paper in excess of the reel side diameters to permit sealing two sides together all around the reel (see figure 2). The additional barrier material shall permit the opening and re-sealing of the barrier paper if examination of or work on the tape is required. Sealing process for barrier material shall not injure the tape. After installing the tape on reel and covering the barrier material, wooden cleats shall be installed around the edge of reel, as shown on the applicable NAEC Drawing 506733, 613516, or 510534.

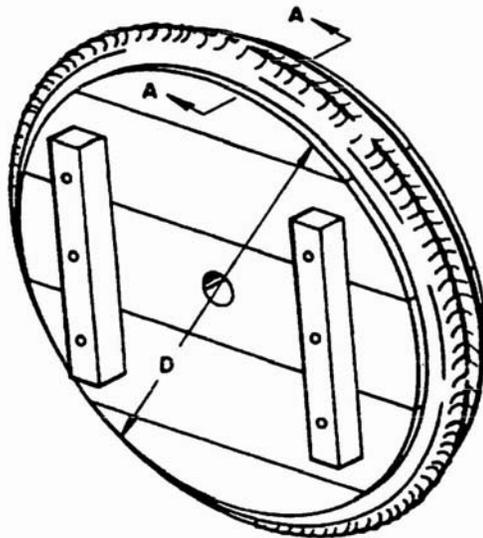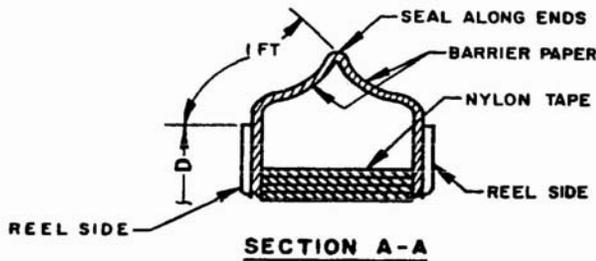

D: DIA OF REEL SIDE

FIGURE 2. Barrier material placement on reel.

MIL-DTL-81736A(AS)

3.5.2.2. Marking. Each reel shall be durably and legibly marked as follows:

TAPE, TEXTILE, NYLON, FOR LANDBASED ARRESTING GEAR, 8-INCH

NAEC Part No.

Stock No.

Serial No.

Manufacturer's Identification Number for the Material Contract or Order No.

Date of Manufacture

Name of Contractor

Name of Manufacturer (if not the same as contractor)

3.5.2.3 Reel manufacture. The reel shall be manufactured as shown on NAEC Drawing 508306. NAEC assigns new part numbers to Drawing 508306 for lengths not specified on the applicable NAEC Drawing 506733, 613516, or 510534.

3.6 Identification.

3.6.1 Manufacturer's identification. The binder warp shall have at the center of the tape, two ends dyed to match the shade assigned to that manufacturer in accordance with MIL-STD-1480. A manufacturer not listed in MIL-STD-1480 shall apply for assignment of color coding (see 6.2 and 6.4). The colorfastness of this yarn shall be rated as "Fair" or "Good" when tested as specified in 4.5.

3.7 Fiber identification. Each roll of tape shall be labeled, ticketed, or invoiced for fiber content in accordance with 16 CFR Part 303.

3.8 Resin treatment of tape. The tape shall be impregnated with resin Spraylat TR-5418-3, containing 3 parts per hundred (PHR) carbon black (based on 100 parts resin) to be used for pigmentation and sunlight protection. The resin shall be applied from a water dispersion, dried and cured to form a firm, adherent and even deposit or coating on the yarns of the tapes (see 6.7).

3.8.1 Extractable matter. The extractable matter from the resin treated webbing shall be not less than 4 and shall be not greater than 8.5 percent by weight.

3.9 Workmanship. The finished tape shall be uniform in quality, free from foreign matter and irregular defects that can adversely affect usage or durability.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as conformance inspection (see 4.2).

MIL-DTL-81736A(AS)

4.2 Conformance inspection. Conformance inspections shall consist of all the visual examinations and tests specified in 4.5 thru 4.6.4.2 (see 6.6).

4.3 Sampling for conformance inspection. Sampling for conformance inspection shall be determined in accordance with 4.3.1 thru 4.3.4.1 and as specified in table II.

4.3.1 Sampling plan A. Tests shall be conducted on every production tape length.

4.3.2 Sampling plan B. Tests shall be conducted on one sample for each continuous loom run.

4.3.3 Sampling plan C. Tests shall be conducted on samples taken prior to weaving from every 10,000 pounds of yarn or fraction thereof.

4.3.4 Sampling plan D. For this inspection, sampling shall be conducted in accordance with 4.3.4.1.

4.3.4.1 Inspection levels. The inspection levels for sampling plan D shall be as follows:

a. Yard-by-yard. A one yard unit of each production tape shall be inspected as specified in 4.6.4.1.

b. Overall. Each production tape length shall be examined for the defects specified in 4.6.4.2.

4.4. Test conditions and preparation. Unless otherwise specified in the detailed test methods herein, the physical tests contained in this specification shall be made with an atmosphere having a relative humidity not greater than 65 percent and a temperature ranging between 50 to 90 °F.

4.5 Tests.

4.5.1 Test methods. Unless otherwise specified, the examinations and tests in table II shall be conducted in accordance with the identified methods. The average of the determinations for a test specified in the specification shall meet the applicable section 3 physical and chemical requirements of this specification. Failure of any sample of tape to conform to the requirements specified in section 3 shall be cause for rejection of the lot represented.

MIL-DTL-81736A(AS)

TABLE II. Test and test methods.

Sampling Plan	Test	Test Method
A	Width, treated	ASTM-D3774, Option A
A	Thickness, treated	ASTM-D1777, Option B
A	Weight, treated	ASTM-D3776, Option B
A	Length, treated	ASTM-D3373, Option C
A	Breaking strength, as woven	4.5.2
B	Ends in warp, as woven Ground Binder Stuffer	Visual Visual Visual
B	Filling, yarns per inch, as woven	ASTM-D3775
B	Yarn ply, as woven Ground Binder Stuffer Filling	Visual Visual Visual Visual
B	Ply Twist, turns per inch, as woven Ground Binder Stuffer Filling	ASTM-D1423 <u>1/</u> ASTM-D1423 <u>1/</u> ASTM-D1423 <u>1/</u> ASTM-D1423 <u>1/</u>
B	Weave, as woven	Figure 1
B	Stiffness, as woven	4.5.3
C	Colorfastness to laundering, as woven	AATCC-61 <u>2/</u>
C	Melting Point, as woven	ASTM-D276 <u>3/</u>
C	Denier, as woven	ASTM-D1907, Option 1 <u>3/</u>
C	Filament count, as woven	Visual
D	Classification of Defects, as woven Yard-by-yard Overall	4.6.4.1 4.6.4.2

1/ Five samples each of the ground, binder, stuffer, and filler yarns from woven tape shall be tested.

2/ Applicable only to manufacturer's identification yarns.

3/ See 6.2 and 6.5.

4.5.2 Breaking strength. The breaking strength test shall be conducted in accordance with 4.5.2.2. The type and capacity of the tensile testing machine shall be applicable to the type of tape undergoing tests. The machine shall be adjusted so that no-load separation of the grips or pulling jaws shall be at the rate of travel specified herein. All breaking tests shall be made on full width sections of tape. Two satisfactory sample tests of each three samples tested shall meet

MIL-DTL-81736A(AS)

the tape strength requirement of the specimen. Jawbreaks are a failure and shall not be a valid test.

4.5.2.1 Test grips. The test grips for holding the specimen shall be so designed that tape failure below 150,000 pounds shall not occur within the grip. The no-load rate of jaw separation shall be 4 to 8 inches per minute.

4.5.2.2 Tape ultimate strength tests. A test specimen, 15 feet long, shall be obtained as specified in 4.5.2.3. The specimen shall be load tested.

4.5.2.3 Method of sampling for breaking strength tests. The first section of tape leaving a loom run shall have a 15-foot specimen removed from the lead end. After this, a 15-foot specimen shall be removed immediately following every other, or alternate, production tape. The rolls of tape shall be marked consecutively as they leave the loom, with the 15-foot specimens marked identically with the rolls of tape to which they apply. Test the first 15-foot specimen leaving the loom run and every 15-foot specimen thereafter. For example, the three 15-foot specimens are tested as outlined in 4.5.2.2. Then, the tests may result in one of the following seven possibilities as specified in 4.5.2.3.1 thru 4.5.2.3.7 (see figure 3).

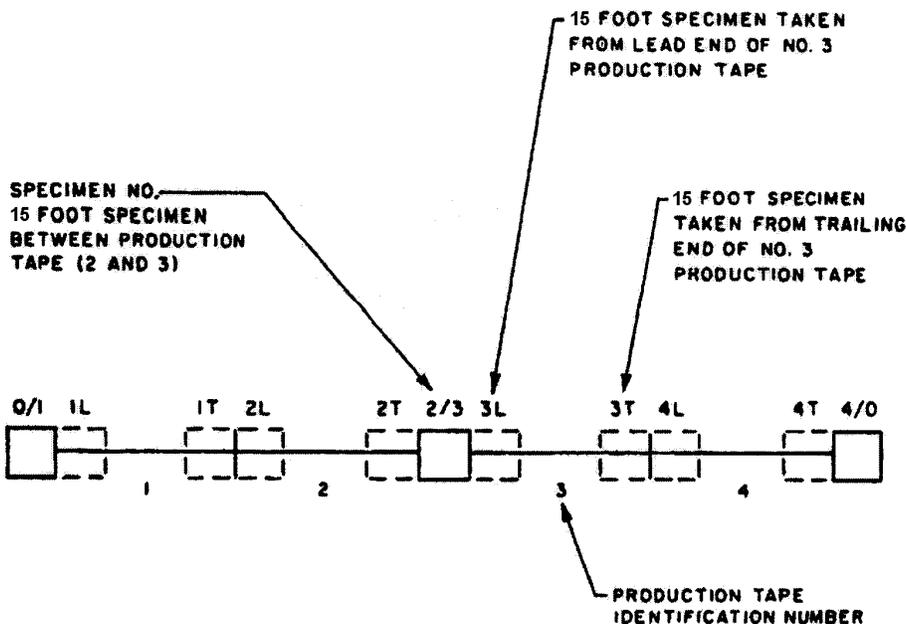


FIGURE 3. 4 - Tape loom run.

4.5.2.3.1 Test result I. If the three tape specimens pass the strength test, the four production tapes in between them are satisfactory.

4.5.2.3.2 Test result II. If the first specimen leaving the loom run fails the strength test and the other two specimens pass the strength test, the third and fourth production tapes are

MIL-DTL-81736A(AS)

satisfactory but a 15-foot specimen shall then be cut from the lead end of the first production tape and tested in order to determine if the first and second tapes are satisfactory. If this specimen passes, the first and second production tapes are satisfactory. If the specimen fails, the first production tape is unsatisfactory. A 15-foot specimen shall then be cut from the trailing end of the first production tape in order to determine if the second production tape is satisfactory.

4.5.2.3.3 Test result III. If the second specimen fails and the first and third pass the strength test, a 15-foot specimen shall be taken from the trailing end of the second production tape and the leading end of the third production tape. If these two specimens pass, all production tapes are satisfactory. If one or both of these specimens fail, the second and third production tape are unsatisfactory. A 15-foot specimen shall then be taken from the leading end of the second production tape and the trailing end of the third production tape in order to determine if the first and fourth production tapes are satisfactory.

4.5.2.3.4 Test result IV. If the last specimen leaving the loom run is the only one that fails the strength test, the third and fourth production tapes are the only tapes in doubt. A 15-foot specimen shall be taken from the trailing end of the fourth production tape and tested. If this specimen passes the strength test, the third and fourth production tapes are satisfactory. If the specimen fails, the fourth production tape is unsatisfactory. A 15-foot specimen shall then be taken from the leading end of the fourth production tape in order to determine if the third production tape is satisfactory.

4.5.2.3.5 Test result V. If the first and second specimens fail the strength test, a 15-foot specimen shall be taken from the trailing end of the second production tape and the leading end of the third production tape.

4.5.2.3.5.1 Case I. If one or both test specimens 2T and 3L pass the strength test, the third, and fourth production tapes are satisfactory. A 15-foot specimen shall then be taken from the leading end of the first production tape and tested. If this specimen passes, the first and second tapes are satisfactory. If this specimen fails, the first production tape is unsatisfactory and the second production tape is in doubt. A 15-foot specimen shall be taken from the trailing end of the first production tape to determine if the second production tape is satisfactory.

4.5.2.3.5.2 Case II. If one or both test specimens 2T and 3L fail the strength test, the second and third production tapes are unsatisfactory. The first production tape shall be tested by taking a 15-foot specimen from the leading ends of the first and second production tapes. Both specimens shall pass the strength test in order for the first production tape to be satisfactory. The fourth production tape shall be tested by taking a 15-foot specimen from the trailing end of the third production tape.

4.5.2.3.6 Test result VI. If the second and third specimens fail the strength test, a 15-foot specimen shall be taken from the trailing end of the second production tape and the leading end of the third production tape.

MIL-DTL-81736A(AS)

4.5.2.3.6.1 Case I. If the specimens 2T and 3L pass the strength test, the first and second production tapes are satisfactory and the third and fourth production tapes shall be tested by taking a 15-foot specimen from the trailing end of the fourth production tape. If this specimen passes the strength test, the third and fourth production tapes are satisfactory. If the specimen fails the strength test, the fourth production tape is unsatisfactory and a 15-foot specimen then shall be taken from the leading end of the fourth production tape in order to determine if the third production tape is satisfactory.

4.5.2.3.6.2 Case II. If one or both test specimens 2T and 3L fail the strength test, the second and third production tapes are unsatisfactory. A 15-foot specimen shall be taken from the trailing ends of the third and fourth production tapes. If one or both specimens fail the strength test, the fourth production tape is unsatisfactory. The first production tape shall then be tested by taking a 15-foot specimen from the leading end of the second production tape.

4.5.2.3.7 Test result VII. If all specimens fail, all tapes represented by that run fail.

4.5.3 Stiffness test. The stiffness test shall be conducted as shown on figure 4. A deflection of one inch shall result when a test load of $75 + 20$ pounds, or $75 - 10$ pounds is applied. Length of the as woven specimen shall be 12 inches.

4.5.3.1 Test fixtures. The test fixture shall be provided by the tape supplier. The fixture consists of three pieces of 2-inch bar stock, each at least 12 inches long of a suitable material, mounted in a loading machine or device as shown on figure 4.

4.5.3.2 Test procedure. The tape specimen shall be installed with the woven edges; i.e., not the cut ends, parallel to the center lines of the two lower bars and centered in the fixture. The load shall be applied by means of the upper bar which is parallel to the lower bars and the load and deflection recorded.

MIL-DTL-81736A(AS)

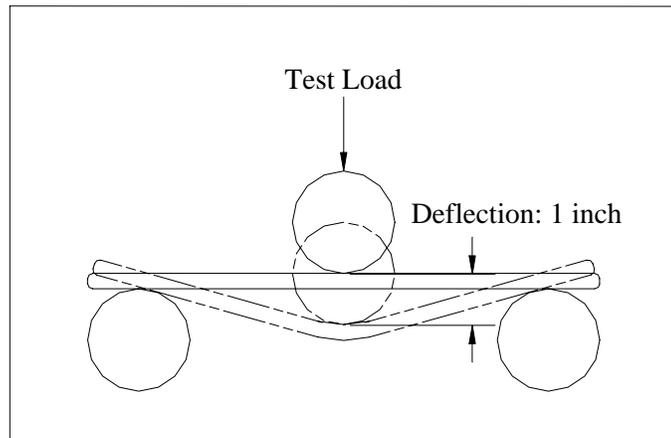
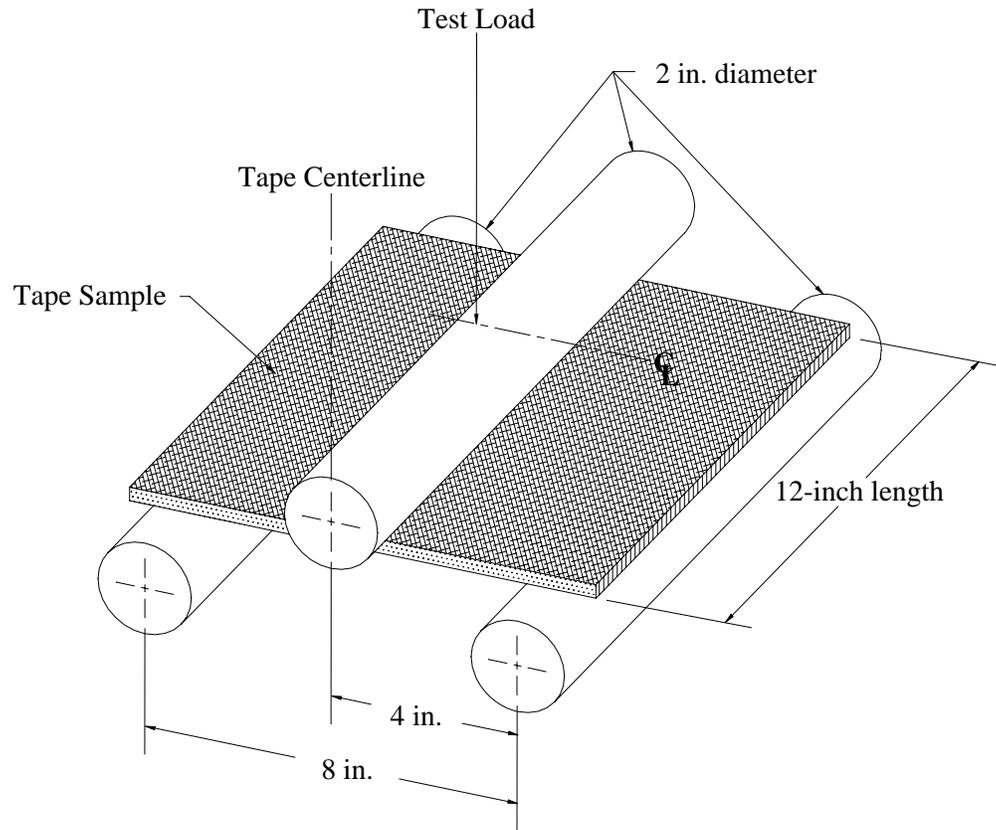


FIGURE 4. Stiffness test.

MIL-DTL-81736A(AS)

4.5.4 Extractable matter. The extractable matter, inclusive of the resin deposit, shall be determined on one specimen of approximately 10 grams of the webbing. The sample, after separation of the warp and filling yarns, shall be dried to constant weight in a weighing bottle at a temperature of 220 ± 8 °F. The specimen shall then be placed in a Soxhlet apparatus and after a 6-hour extraction with methyl-ethyl-ketone, the final weight of the extracted sample shall be obtained by repeating the constant weight drying conditions as specified above. The percent of extractable matter shall be calculated as follows:

$$\text{Percent extractable matter} = \frac{\text{Loss in weight on extraction}}{\text{Original dry weight on sample}} \times 100$$

4.6.4 Classification of defects. Defects found during the examination shall be classified in accordance with 4.6.4.1 through 4.6.4.2.

4.6.4.1 Yard-by-yard examination. A one-yard unit of tape as indicated in 4.3.4.1a shall be examined and visual defects classified as listed in table III. This examination may be performed on the as woven tape. The defects found shall be counted regardless of their proximity to each other except where two or more defects represent a single local condition of the tape, in which case only the more serious defects shall be counted. A continuous defect shall be counted as one defect for each warpwise yard, or fraction thereof, in which it occurs.

4.6.4.2 Overall examination. Examine required samples for finish, odor, and cleanliness. The finish shall be equal to approved sample, when available (see 6.3). There shall not be any objectionable odor and the samples shall be clean.

MIL-DTL-81736A(AS)

TABLE III. Classification of defects.

DEFECTS	DESCRIPTION	CRITICAL	MAJOR	MINOR
Abrasion marks	Resulting in the rupture of yarns, or in the nap sufficient to obscure the identity of any yarn exceeding 10 percent of width or one inch in length.	X		
Broken or missing end	Two or more regardless of length of a single end exceeding 6 inches in length. Single end under 6 inches but exceeding ¼ inch.	X		X
Broken or missing pick	Two or more regardless of extent. NOTE: The filling tie-in or joining shall not be construed as a defect of any nature.	X		
Coarse or light filling bar	Resulting in visible difference in stiffness or thickness of tape and extending for more than ¼ inch or less in the length direction.	X		
Twist or distortion	Tape will not lay flat upon application of manual pressure due to twist or distortion.			X
Cut, hole, or tear	Any cut, hole, or tear.	X		
Drop-ply	Clearly visible on more than two ends within same length and extending over 9 linear inches or more.		X	

MIL-DTL-81736A(AS)

TABLE III. Classification of defects - Continued.

DEFECTS	DESCRIPTION	CRITICAL	MAJOR	MINOR
Edge loop	Forming clearly visible filling loops, or edges tied loosely to body of webbing for 2 linear inches or more.	X		
Edge cut, torn, or frayed	Clearly visible along edge.	X		
Edge scalloped	Any indentation of edges above allowable tolerances.		X	
Floats or skips	Multiple, ½ inch or more in combined warp and filling direction or single float or skip over more than 1 inch. Multiple, less than ½ inch in combined warp or filling directions, or single float or skip over more than ½ inch, but not exceeding 1 inch if in warp, or more than ¼ inch of the width but not exceeding 1 inch if in filling.			X
Hitchback, crack, open place	Clearly visible opening between adjoining picks, or warpwise tension area over part of the width resulting in visible light and heavy place.	X		
Jerked-in, filling, slough-off, slug	A clearly visible loop of filling pulled in at edges.			X
Kinks	More than 3 in any 9 linear inches.		X	
Knots	More than 1 knot in any 5 linear inches. One knot every 2 yards with untrimmed ends extending from surface of tape.		X	

MIL-DTL-81736A(AS)

TABLE III. Classification of defects - Continued.

DEFECTS	DESCRIPTION	CRITICAL	MAJOR	MINOR
Mispick, double pick	Two or more across the full width. Single across the full width.			X
Slack end	Two or more in the same length, jerked in between picks, or forming clearly visible loops on the surface.	X		
Slub or slag, gout	More than twice the thickness of the yarn (or ply, if plied).			X
Smash	Any smash.	X		
Spot, stain, or streak	Any clearly visible dirt, rust, grease, oil, spot, stain or streak.			X
Wrong draw	Extending for more than 9 inches		X	
Identification threads	Misplaced.			X
Identification threads	Missing.	X		
END ITEM PREPARATION DEFECTS				
Marking	Omitted, illegible, location, sequence, or method of application.		X	
Materials	Any component missing. Any component damaged, affecting serviceability.	X		
Workmanship	Not uniform in quality. Contains foreign matter. Contains irregular defects. Bulging or distortion of container.		X	

MIL-DTL-81736A(AS)

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The nylon tape covered by this specification is intended for use in landbased aircraft arresting gear.

6.2 Acquisition requirements. Acquisition documents should specify the following:

- a. Title, number, and date of this specification.
- b. Size.
- c. Quantity desired.
- d. Length of roll required (see 3.5.1).
- e. Manufacturer's identification (see 3.6.1).
- f. Conformance test report (see 4.2).
- g. Packaging requirements (see 5.1).
- h. Certificate of compliance for type of nylon, denier, melting point, filament count, bright, high tenacity, light and heat resistant nylon yarn (see 6.5).
- i. Actual test report or inspection data for type of nylon, denier, melting point, filament count, bright, high tenacity, light and heat resistant nylon yarn (see 6.5.1).

6.3 Standard sample. For access to the standard sample, address the procuring activity issuing the invitation for bids.

6.4 Assignment of color coding for manufacturers' identification. Manufacturers not listed in MIL-STD-1480 must apply to Commander, US Army Natick Research and Development Command, Natick, Massachusetts 01760 for assignment of color coding.

6.5 Verification of compliance for type of nylon, denier, melting point, and filament count requirements. A certificate of compliance is required from the yarn manufacturer for verification that the requirements for the type of nylon, denier, melting point, filament count, bright, high tenacity, light and heat resistant nylon yarn are met (see 6.5.1).

MIL-DTL-81736A(AS)

6.5.1 Test report. The certification of compliance for yarn should be accompanied by verifiable actual test or inspection data for the type of nylon, denier, melting point, filament count, bright, high tenacity, light and heat resistant nylon yarn (see 6.2).

6.6 Responsibility for inspection. Unless otherwise specified in the contract or order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to ensure supplies and services conform to specified requirements.

6.7 Resin. Spraylat Resin TR-5418-3 is available from the Spraylat Corporation, 716 South Columbus Avenue, Mount Vernon, NY 10550.

6.8 Subject term (keyword) listing.

Bag
Container
Denier
Fiber
Reclosable
Weave
Yarn

6.9 Identification of changes. Marginal notations are not used in this revision to identify changes with respect to the previous issue, due to the extent of the changes.

Custodian:
Navy - AS

Preparing activity:
Navy - AS

Project No. 8315-2006-005

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using ASSIST Online database at <http://assist.daps.dla.mil>.