

| |
|------------|
| INCH POUND |
|------------|

MIL-DTL-43511D
12 October 2006

SUPERCEDING
MIL-V-43511C
16 July 1990

DETAIL SPECIFICATION

VISORS, FLYER'S HELMET, POLYCARBONATE

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers general and performance requirements for curved polycarbonate flyer's helmet visors worn by aircrew personnel.

1.2 Classification. The visors will be of the following classes as specified (see 6.2).

| | | |
|---------|---|-----------------------------------|
| Class 1 | - | Clear |
| Class 2 | - | Neutral Gray |
| Class 3 | - | Neutral Gray Gradient (Air Force) |

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3, 4, or 5 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements documents cited in sections 3, 4, or 5 of this specification, whether or not they are listed.

| |
|---|
| <p>Comments, suggestions, or questions on this document should be addressed to the Commander, Defense Supply Center Philadelphia, ATTN: DSCP-FQSE, 700 Robbins Avenue, Philadelphia, PA 19111-5092 or e-mailed to Kathleen.Gullifer@dla.mil. Since contract information can change, you may want to verify the currency of this address information using the ASSIST Online database at http://assist.daps.dla.mil.</p> |
|---|

AMSC N/A

FSC 8415

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

MIL-DTL-43511D

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract (see 6.2).

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-E-12397 Eraser, Rubber-Pumice (for Testing Coated Optical Elements)

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-662 V₅₀ Ballistic Test For Armor
MIL-STD-810 Environmental Engineering Considerations and Laboratory Tests

(Copies of these documents are available online at <http://assist.daps.dla.mil> or from the Standardization Documents Order Desk, 700 Robbins Avenue, Building 4D, Philadelphia, PA 19111-5094.)

2.2.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DRAWING

7680606 Tester, Abrasion, Optical Coating

2.3 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract (see 6.2).

AMERICAN NATIONAL STANDARDS INSTITUTE (ANSI)

ANSI Z87.1 Occupational and Educational Personal Eye
And Face Protection Devices

(Copies of this document are available from www.ansi.org<BLOCKED::http://www.ansi.org/> or the American National Standards Institute, 25 West 43rd St., 4th Floor, New York, NY 10036.)

ASTM International

ASTM F 735 Standard Test Method for Abrasion Resistance of
Transparent Plastics and Coatings Using the Oscillating
Sand Method
ASTM D 1003 Standard Test Method for Haze and Luminous
Transmittance of Transparent Plastics

MIL-DTL-43511D

| | |
|-------------|---|
| ASTM D 1044 | Standard Test Method for Resistance of Transparent Plastics to Surface Abrasion |
| ASTM D 3935 | Standard Specification for Polycarbonate (PC) Unfilled and Reinforced Material |
| ASTM D 3359 | Standard Test Method for Measuring Adhesion by Tape Test |

(Copies of these documents are available from www.astm.org<BLOCKED::http://www.astm.org/> or the ASTM International, 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959.)

AMERICAN SOCIETY FOR QUALITY

| | |
|---------------|---|
| ANSI/ASQ Z1.4 | Sampling Procedures and Tables For Inspection by Attributes (DoD adopted) |
|---------------|---|

(Copies of this document are available from www.asq.org<BLOCKED::http://www.asq.org/> or the American Society for Quality, 600 North Plankinton Ave., Milwaukee, WI 53203-2914 or www.ansi.org<BLOCKED::http://www.ansi.org/> or the American National Standards Institute, 25 West 43rd St., 4th Floor, New York, NY 10036.)

INTERNATIONAL COMMISSION ON ILLUMINATION (CIE)

CIE 1924 Standard

(Copies of these documents are available from www.cie-usnc.org<BLOCKED::http://www.cie-usnc.org/> or the CIE/USA Publications Office, c/o TLA-Lighting Consultants, Inc., 7 Pond St., Salem, MA 01970.)

2.4 Order of precedence. In the event of a conflict between the text of this document and the references cited herein (except for related specification sheets), the text of this document takes precedence. Nothing in this document however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 First article. When specified (see 6.2), a sample shall be subjected to first article inspection in accordance with 4.2.

3.2 Design and dimensions. The design and dimensions of the visor shall be as specified in the end item specification, drawing or contract as applicable.

3.3 Materials and components. Unless otherwise specified in the end item specification, drawing, or contract as applicable, the visor shall be fabricated from bisphenol type polycarbonate plastic molding material conforming to ASTM D 3935. All other material and components used in the construction of the visor shall be as specified in the end item specification, drawing, or contract, as applicable.

3.3.1 Recycled, recovered, or environmentally preferable materials. Recycled, recovered, or environmentally preferable materials should be used to the maximum extent possible provided that the material meets or exceeds the operational and maintenance requirements, and promotes economically advantageous life cycle costs.

MIL-DTL-43511D

3.4 Areas of vision. Unless otherwise specified, the visor shall have three areas of vision which are identified as: outside the area of vision (no optical requirement), non-critical area of vision, and critical area of vision. The center point for the right and left optics shall be identified as point "C". The location of point "C" and the location and size of the three areas of the visor identified above shall be as specified in the end item specification, drawing, or contract as applicable. The critical area is approximately a 50 degree radius field of view from the primary line of sight intercept point on the visor for the designed right and left eye locations. The areas within 1 mm (1/16") of the edges of the visor are non-critical areas. Regions that rest against the helmet shell are outside the area of vision. Figure 1 shows a typical layout of a visor and is intended to serve as a guide only for use by Government agencies to develop their detailed requirements. Unless otherwise specified in the end item specification, drawing, or contract as applicable, the numbered circles within the critical areas are designated as points of choice for prismatic and distortion tests. Points bearing the same number, for example 5R and 5L, shall be compared with each other, except points 2R and 2L (outermost points on left and right sides of visor) shall be compared with point 3 (center point of visor) when measuring refractive power or prismatic deviations.

3.5 Performance.

3.5.1 Prismatic deviation. Prismatic deviation stated herein includes the inherent prismatic power resulting from nonparallel surfaces of the material and dissimilar curvature between the critical areas. The vertical and horizontal prismatic deviations shall be tested as specified in 4.3.5.

3.5.1.1 Vertical prismatic deviation. The vertical prismatic deviation through point "C" for the left and right eyes shall be no more than 0.18 prism diopters. The vertical prism along any individual line of sight through the critical area shall not exceed 0.25 prism diopters.

3.5.1.2 Horizontal prismatic deviation. The horizontal prismatic deviation through point "C" for the left and right eyes shall be no more than 0.18 prism diopters BASE IN and no more than 0.25 diopters BASE OUT. The horizontal prism along any individual line of sight through the critical area shall not exceed 0.25 prism diopters.

3.5.2 Refractive power. The refractive power shall not exceed plus or minus 0.125 diopters at point "C" and at all other points of choice for the left and right optics, when tested as specified in 4.3.5.

3.5.3 Luminous transmittance (see 6.5)

3.5.3.1 Class 1 visor. The luminous transmittance of class 1 visor shall be not less than 85 percent throughout the critical area when tested as specified in 4.3.5.

3.5.3.2 Class 2 visor. The luminous transmittance of class 2 visor shall be within 12 to 18 percent when measured at point "C", left and right optics. The total visible transmittance of the visor shall not vary more than 3.0 percentage points. Tests shall be as specified in 4.3.5.

3.5.4 Optical density.

3.5.4.1 Class 3 visor. The optical density (OD) of the class 3 visor shall be between 0.83 and 0.60 OD when measured at point "C" left and right optics. The OD at any point in a horizontal meridian of a given visor shall not vary by more than 0.1 OD from other points on the same meridian. The class 3 visor shall consist of a class 1 visor with a gradient tint, darker at the top, conforming to an OD gradient of 0.4 OD/inch \pm 0.06 OD when measured at point "C" to a

MIL-DTL-43511D

vertical distance of 1-inch above or below point "C". The resultant gradient shall be smooth and uniform when tested as specified in 4.3.5.

3.5.5 Optical distortion of critical areas. The optical distortion within the critical vision areas shall conform to the acceptable standards shown on figure 2 when tested as specified in 4.3.5.

3.5.6 Haze. The haze value of the visor shall not exceed 2.0 percent when tested as specified in 4.3.5.

3.5.7 Ultraviolet transmittance. The erythema ultraviolet transmittance shall not be more than 1.00 percent, when computed as the average spectral transmittance at wavelengths of 290, 300, 310, and 320 nm when tested as specified in 4.3.5.

3.5.8 Neutrality of class 2 and 3 visors. The spectral transmittance (see 6.6) of the class 2 visor may vary with wavelengths between 430 and 730 nm, the average percentage deviation within nine spectral bands shall be less than 12 when tested as specified in 4.3.5. The spectral distribution curve shall show a reasonable even distribution throughout the visible spectrum to insure that color distortion will not be excessive. The neutrality of the class 3 visor shall conform to the requirements specified for the class 2 visor except that the average percentage deviation shall be less than 20 when tested as specified in 4.3.5.

3.5.9 Chromaticity of class 2 and 3 visors. The chromaticity coordinates x and y of the classes 2 and 3 visors shall be within the limits indicated on figure 3 when computed as described in 4.3.5.

3.5.10 Ballistic resistance. The ballistic resistance of the lenses shall be such that they will pass a V₀ test using a 0.22 caliber, 17.0 ± 0.5 grain, T37 shaped projectile at a velocity of 550 to 560 feet per second when tested as specified in 4.3.5.

3.5.11 Abrasion resistant coating. After being subjected to the abrasion tests specified in 4.3.5, the increase in haze shall not exceed 2 percent and the decrease in transmittance shall not exceed 2 percent.

3.5.12 Bayer abrasion resistance. After being subject to the Bayer abrasion test the Bayer ratio shall exceed a value of 4.0 or higher as specified in 4.3.5.

3.5.13 Coating adhesion. Before and after humidity exposure, the visor shall show no loss of coating when tested in accordance with 4.3.5.

3.5.14 Weathering resistance. The coated visors shall show no yellowing or other changes, nor show loss of coating when tested as specified in 4.3.5.

3.5.15 Chemical resistance. When tested in accordance with 4.3.5 the visor shall not increase more than 2% for transmittance and haze.

3.6 Workmanship. The visors shall be free from all defects which would affect proper functioning in service. The visors shall conform to the quality and grade of product established by this specification.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

- a. First article inspection (see 4.2)

MIL-DTL-43511D

b. Conformance inspection (see 4.3)

4.2 First article inspection. When a first article is required (see 3.1), it shall be examined as specified in 4.3.3 and 4.3.4 and tested for the characteristics specified in 4.3.5. Any nonconformance shall be cause for the rejection of the first article. The number of units to be inspected shall be specified in the contract.

4.3 Conformance inspection. Unless otherwise specified, sampling for inspection shall be performed in accordance with ASQ-Z1.4. Items shall be examined as specified in 4.3.3 and 4.3.4 and tested for the characteristics specified in 4.3.5.

4.3.1 Inspection lots. For purposes of sampling, a lot shall consist of visors produced from a single batch of resin during one continuous injection molding operation. Any shutdown of the molding operation shall be considered as the termination of that operation and lot.

4.3.2 Component and material inspection. Components and materials shall be inspected in accordance with all the requirements of referenced documents unless otherwise excluded, amended, modified, or qualified in this specification or applicable purchase document.

4.3.3 End item visual examination. The end item shall be examined for the defects listed in Table I. The lot size shall be expressed in units of visors. The sample unit shall be one visor.

TABLE I. End item visual defects

| Examine | Defect | Classification | | |
|------------|--|----------------|-------|-------|
| | | Critical | Major | Minor |
| Appearance | Pit, bubble, scratch, foreign matter, void, inclusions or blister: | | | |
| | - Critical area of vision | 1 | | |
| | - Non-critical area of vision | | 101 | |
| | - Area outside area of vision | | | 201 |
| | Cloudiness: | | | |
| | - Critical area of vision | 2 | | |
| | - Non-critical area of vision | | 102 | |
| | Crack, hole, chip, or break: | | | |
| | - Any area | 3 | | |
| | - Evidence of warpage | 4 | | |
| | Visible striae or waviness: | | | |
| | - Critical area of vision | 5 | | |
| | - Non-critical area of vision | | 103 | |
| | Surface abraded, dulled, or not smooth: | | | |
| | - Critical area of vision | 6 | | |
| | - Non-critical area of vision | | 104 | |

MIL-DTL-43511D

TABLE I. End item visual defects (continued)

| Examine | Defect | Classification | | |
|---------|---|----------------|-------|-------|
| | | Critical | Major | Minor |
| | Stain or discoloration not readily removed with water: | | | |
| | - Critical area of vision | 7 | | |
| | - Non-critical area of vision | | 105 | |
| | Sharp edge or burr: | | | |
| | - Affecting serviceability | | 106 | |
| | - Not affecting serviceability | | | 202 |
| | Transmittance gradient not smooth and uniform (class 3 visor) | 8 | | |
| Design | Not as specified | 9 | | |

4.3.4 End item dimensional examination. The visors shall be examined for conformance to the dimensions specified in the end item specification, drawings, or contract. Any dimension not within the specified tolerance shall be classified as a critical defect.

4.3.5 End item testing. The visors shall be tested for the characteristics listed in Table II.

TABLE II. End item tests

| Characteristic | Requirement paragraph | Test method | Number of determinations | Results to nearest |
|--------------------------------------|-----------------------|-------------|--|--------------------|
| Prismatic deviation | 3.5.1 | 4.4.1 | 1/unit | 0.01 diopter |
| Refractive Power | 3.5.2 | 4.4.2 | 2/unit | 0.01 diopter |
| Luminous transmittance | 3.5.3 | 4.4.3 | 1/unit for class 1 2/unit for class 2 | 1 percent |
| Optical density | 3.5.4 | 4.4.4 | 2/unit for class 3 | 1 percent |
| Optical distortion of critical areas | 3.5.5 | 4.4.5 | 1/unit | Pass or fail |
| Haze | 3.5.6 | 4.4.6 | 1/unit | 0.1 percent |
| Ultraviolet transmittance <u>1</u> / | 3.5.7 | 4.4.7 | 1/unit | 1 percent |

MIL-DTL-43511D

TABLE II. End item tests (continued)

| Characteristic | Requirement paragraph | Test method | Number of determinations | Results to nearest |
|-------------------------------|-----------------------|-------------|--------------------------|--------------------|
| Neutrality of class 2 and 3 | 3.5.8 | 4.4.8 | 1/unit | 1 percent |
| Chromaticity of class 2 and 3 | 3.5.9 | 4.4.9 | 1/unit | 1 percent |
| Ballistic resistance | 3.5.10 | 4.4.10 | <u>2</u> / | Pass or fail |
| Abrasion resistance | 3.5.11 | 4.4.11 | 2/unit | <2 percent |
| Bayer abrasion resistance | 3.5.12 | 4.4.12 | 2/unit | ratio >4 |
| Coating adhesion | 3.5.13 | 4.4.13 | 2/unit | Pass or fail |
| Weathering Resistance | 3.5.14 | 4.4.14 | 1/unit | Pass or fail |
| Chemical resistance | 3.5.14 | 4.4.15 | 2/unit | <2 percent |

1/ The test for ultraviolet transmittance shall be performed only on the first lot of visors from each batch of molding material.

2/ A minimum of three articles.

4.4 End item performance test methods.

4.4.1 Prismatic deviation test. Prismatic deviation shall be measured in accordance with ANSI Z87.1. Telescope, lensometer or optical beam deviation along the selected line of sight may be used. Error shall be less than 0.03 prism diopters.

4.4.1.1 Vertical prismatic deviation. BASE UP prism shall be designated positive (+) while BASE DOWN prism shall be designated negative (-). The vertical prismatic imbalance shall be defined as the absolute value of the difference between the prism through point "C" of the right and left eyes. Vertical prismatic imbalance shall meet the requirements as specified in 3.5.1.1. This calculation can also be applied to other opposing points as stated in 3.4.

4.4.1.2 Horizontal prismatic deviation. BASE OUT prism shall be designated positive (+) while BASE IN prism shall be designated negative (-). The horizontal prismatic imbalance shall be defined as the absolute value of the sum of prism at the design eye point of the right and left lenses. Horizontal prismatic imbalance shall meet the requirements specified in 3.5.1.2. This calculation can also be applied to other opposing points as stated in 3.4.

MIL-DTL-43511D

4.4.2 Refractive power test. The refractive power shall be determined with any suitable instrument with increments of 0.01 diopters for spherical and cylindrical powers. The aperture over the test items shall not exceed 1 centimeter. If the instrument used cannot measure astigmatic components, then the target pattern shall be a fixed spoke wheel, with a minimum of 24 spokes.

4.4.3 Luminous transmittance test. The transmittance shall be measured through point “C” (see 3.4) for left and right eye, using a calibrated National Institute of Standards and Technology (NIST) traceable spectrophotometer with a spectral bandwidth ≤ 10 nm. Table III shows an example calculation of the photopic and scotopic luminous transmittance.

TABLE III. Sample calculation for luminous transmittance 1/ 2/ 3/ 4/ 5/

| Wavelength (nm) | V(λ) | V(λ') | Sample T | V(λ)*T | V(λ')*T |
|-----------------|----------------|-----------------|----------|------------------|-------------------|
| 380 | 0.00004 | 0.00059 | 0.00003 | 0.00000 | 0.00000 |
| 390 | 0.00012 | 0.00221 | 0.12361 | 0.00001 | 0.00027 |
| 400 | 0.00040 | 0.00929 | 0.65772 | 0.00026 | 0.00611 |
| 410 | 0.00120 | 0.03484 | 0.83508 | 0.00100 | 0.02909 |
| 420 | 0.00400 | 0.09660 | 0.86258 | 0.00345 | 0.08333 |
| 430 | 0.01160 | 0.19980 | 0.87339 | 0.01013 | 0.17450 |
| 440 | 0.02300 | 0.32810 | 0.87927 | 0.02022 | 0.28849 |
| 450 | 0.03800 | 0.45500 | 0.88191 | 0.03351 | 0.40127 |
| 460 | 0.06000 | 0.56720 | 0.88449 | 0.05307 | 0.50169 |
| 470 | 0.09100 | 0.67560 | 0.88644 | 0.08067 | 0.59888 |
| 480 | 0.13900 | 0.79300 | 0.88830 | 0.12347 | 0.70442 |
| 490 | 0.20800 | 0.90430 | 0.88673 | 0.18444 | 0.80187 |
| 500 | 0.32300 | 0.98170 | 0.88690 | 0.28647 | 0.87067 |
| 510 | 0.50300 | 0.99660 | 0.89154 | 0.44844 | 0.88851 |
| 520 | 0.71000 | 0.93520 | 0.89110 | 0.63268 | 0.83336 |
| 530 | 0.86200 | 0.81100 | 0.88666 | 0.76430 | 0.71908 |
| 540 | 0.95400 | 0.64970 | 0.88772 | 0.84689 | 0.57675 |
| 550 | 0.99500 | 0.48080 | 0.88991 | 0.88546 | 0.42787 |
| 560 | 0.99500 | 0.32880 | 0.88619 | 0.88176 | 0.29138 |
| 570 | 0.95200 | 0.20760 | 0.89049 | 0.84775 | 0.18487 |
| 580 | 0.87000 | 0.12100 | 0.88132 | 0.76675 | 0.10664 |
| 590 | 0.75700 | 0.06550 | 0.88939 | 0.67327 | 0.05826 |
| 600 | 0.63100 | 0.03325 | 0.88914 | 0.56105 | 0.02956 |
| 610 | 0.50300 | 0.01593 | 0.89237 | 0.44886 | 0.01422 |
| 620 | 0.38100 | 0.00737 | 0.89093 | 0.33944 | 0.00657 |
| 630 | 0.26500 | 0.00334 | 0.89280 | 0.23659 | 0.00298 |
| 640 | 0.17500 | 0.00150 | 0.88936 | 0.15564 | 0.00133 |
| 650 | 0.10700 | 0.00068 | 0.90356 | 0.09668 | 0.00061 |
| 660 | 0.06100 | 0.00031 | 0.89687 | 0.05471 | 0.00028 |
| 670 | 0.03200 | 0.00015 | 0.91225 | 0.02919 | 0.00014 |
| 680 | 0.01700 | 0.00007 | 0.90045 | 0.01531 | 0.00006 |
| 690 | 0.00820 | 0.00004 | 0.90968 | 0.00746 | 0.00004 |
| 700 | 0.00410 | 0.00002 | 0.91164 | 0.00374 | 0.00002 |
| 710 | 0.00210 | 0.00000 | 0.90284 | 0.00190 | 0.00000 |
| 720 | 0.00100 | 0.00000 | 0.91709 | 0.00092 | 0.00000 |
| 730 | 0.00050 | 0.00000 | 0.91137 | 0.00046 | 0.00000 |
| 740 | 0.00030 | 0.00000 | 0.90570 | 0.00027 | 0.00000 |
| 750 | 0.00010 | 0.00000 | 0.92346 | 0.00009 | 0.00000 |
| 760 | 0.00010 | 0.00000 | 0.91446 | 0.00009 | 0.00000 |
| TOTALS | 10.686 | 9.707 | 32.905 | 9.496 | 8.603 |

MIL-DTL-43511D

$$T_{\text{photopic}} = \frac{\sum_{\lambda=380}^{760} T * V_{\lambda}}{\sum_{\lambda=380}^{760} V_{\lambda}} = \frac{9.496}{10.686} = 88.87 \quad T_{\text{scotopic}} = \frac{\sum_{\lambda=380}^{760} T * V_{\lambda'}}{\sum_{\lambda=380}^{760} V_{\lambda'}} = \frac{8.603}{9.707} = 88.63$$

1/ $V(\lambda)$ = the photopic relative luminous efficiency (CIE 1924 Standard)

2/ $V(\lambda')$ = the scotopic relative luminosity (CIE 1925 Standard)

3/ T = transmittance of the sample under test (here a Class 1 sample)

4/ $T/\text{photopic}$ = Percent photopic transmittance

5/ $T/\text{scotopic}$ = Percent scotopic transmittance

4.4.4 Optical density of class 3 test. The optical density of the class 3 visors shall be calculated by first determining the luminous transmittance in accordance with ASTM D 1003. The optical density shall be calculated by the formula:

$$\text{Optical Density} = \text{Log} \frac{1}{\text{Transmittance}}$$

4.4.5 Optical distortion of critical areas test. The optical distortion of the critical area of the visors shall be determined by inserting the visor with its surface normal to the line of sight into the apparatus described on figure 4. The degree of off-parallelism shall constitute the amount of distortion. The visor shall be compared with the plates on figure 2.

4.4.6 Haze test. The haze shall be determined in accordance with ASTM D 1003.

4.4.7 Ultraviolet transmittance test. The erythema ultraviolet transmittance shall be measured by a spectrophotometer.

4.4.8 Neutrality of class 2 and 3 visors test. The spectral transmittance of the class 2 or 3 visor, as applicable, shall be measured by a spectrophotometer having a monochromator band width of 10 nm or less and a reproduction of plus or minus 1 percent. The neutrality shall be calculated by the Judd Daylight Duplication Method. Table IV shows an example for the calculation of spectral transmittance deviations.

TABLE IV. Example for calculation of spectral transmittance deviation. 1/ 2/ 3/ 4/ 5/

| Wave length (nm) | T | Band N | Wave length range | Average Transmittance T_n | Percent deviation $100(1-T_n/T_c) \times \text{Weight} = \text{Product}$ | | |
|------------------|-------|--------|-------------------|-----------------------------|--|----|------|
| 430 | 0.114 | | | | | | |
| 440 | 0.118 | | | | | | |
| 450 | 0.127 | | | | | | |
| 460 | 0.137 | 1 | 430-490 | 0.133 | 14.25 | 5 | 71.2 |
| 470 | 0.142 | | | | | | |
| 480 | 0.144 | | | | | | |
| 490 | 0.145 | 2 | 460-520 | 0.145 | 6.34 | 10 | 63.4 |
| 500 | 0.147 | | | | | | |
| 510 | 0.149 | | | | | | |
| 520 | 0.151 | 3 | 490-550 | 0.151 | 2.80 | 10 | 28.0 |
| 530 | 0.153 | | | | | | |
| 540 | 0.154 | | | | | | |

MIL-DTL-43511D

TABLE IV. Example for calculation of spectral transmittance deviation. (cont.) 1/ 2/ 3/ 4/ 5/

| Wave length (nm) | T | Band N | Wave length range | Average Transmittance T _n | Percent deviation 100(1-T _n /T _c) x Weight = Product | | |
|------------------|-------|--------|-------------------|--------------------------------------|--|----|-------|
| 550 | 0.155 | 4 | 520-580 | 0.155 | 0.22 | 10 | 2.2 |
| 560 | 0.157 | | | | | | |
| 570 | 0.158 | | | | | | |
| 580 | 0.159 | | | | | | |
| 590 | 0.160 | 5 | 550-610 | 0.159 | 2.31 | 10 | 23.1 |
| 600 | 0.160 | | | | | | |
| 610 | 0.160 | | | | | | |
| 620 | 0.161 | | | | | | |
| 630 | 0.161 | 6 | 580-640 | 0.160 | 3.39 | 10 | 33.9 |
| 640 | 0.160 | | | | | | |
| 650 | 0.159 | | | | | | |
| 660 | 0.159 | | | | | | |
| 670 | 0.158 | 7 | 610-670 | 0.160 | 3.12 | 10 | 31.2 |
| 680 | 0.157 | | | | | | |
| 690 | 0.156 | | | | | | |
| 700 | 0.153 | | | | | | |
| 710 | 0.151 | 8 | 640-700 | 0.158 | 1.67 | 5 | 8.3 |
| 720 | 0.149 | | | | | | |
| 730 | 0.148 | | | | | | |
| | | | | | | | |
| | | 9 | 670-730 | 0.153 | 1.18 | 1 | 1.2 |
| | | | | | | | |
| | | | | | | | |
| | | | | | | | |
| | | | | | Totals | 71 | 262.5 |

Notes:

1/ T_c = Total visible transmittance of sample visor, which is 0.155.

2/ T = Transmittance at 10 nm intervals.

3/ T_n = Average transmittance of 60 nm band. The T_n for a given band is the average of the seven tabulated values within that band except that the first and last values are divided by 2 and the average computed by dividing the sum of the values by 6.

4/ Average percentage deviation of spectral transmittance within nine spectral bands. (Average deviation – 262.5/71 = (3.7%))

5/ This table is based on illuminant “C”.

4.4.9 Chromaticity of class 2 and 3 visors test. The chromaticity coordinates x and y shall be calculated from spectrophotometric data. Table V illustrates a sample calculation.TABLE V. Sample computation table of coordinates 1/ 2/ 3/ 4/ 5/

| Wavelength (nm) | \bar{x} | \bar{y} | \bar{z} | T | $\bar{x}T$ | $\bar{y}T$ | $\bar{z}T$ |
|-----------------|-----------|-----------|-----------|-------|------------|------------|------------|
| 380 | 4 | | 20 | 0.104 | 0 | 0 | 2 |
| 390 | 19 | | 89 | 0.240 | 5 | 0 | 21 |
| 400 | 85 | 2 | 404 | 0.301 | 26 | 1 | 122 |
| 410 | 329 | 9 | 1,570 | 0.275 | 90 | 2 | 432 |
| 420 | 1,238 | 37 | 5,949 | 0.174 | 215 | 6 | 1,035 |
| 430 | 2,997 | 122 | 14,628 | 0.110 | 330 | 13 | 1,609 |
| 440 | 3,975 | 262 | 19,938 | 0.093 | 370 | 24 | 1,854 |

MIL-DTL-43511D

TABLE V. Sample computation table of coordinates (cont.)1/ 2/ 3/ 4/ 5/

| Wavelength (nm) | \bar{x} | \bar{y} | \bar{z} | T | $\bar{x}T$ | $\bar{y}T$ | $\bar{z}T$ |
|--------------------|-----------|-----------|-----------|--------|---------------|---------------|---------------|
| 450 | 3,915 | 443 | 20,638 | 0.092 | 360 | 41 | 1,899 |
| 460 | 3,362 | 694 | 19,299 | 0.100 | 336 | 69 | 1,930 |
| 470 | 2,272 | 1,058 | 14,972 | 0.110 | 250 | 116 | 1,647 |
| 480 | 1,112 | 1,618 | 9,461 | 0.122 | 136 | 197 | 1,154 |
| 490 | 363 | 2,358 | 5,274 | 0.132 | 48 | 311 | 696 |
| 500 | 52 | 3,401 | 2,864 | 0.140 | 7 | 476 | 401 |
| 510 | 89 | 4,833 | 1,520 | 0.142 | 13 | 686 | 216 |
| 520 | 576 | 6,462 | 712 | 0.142 | 82 | 918 | 101 |
| 530 | 1,523 | 7,934 | 388 | 0.141 | 215 | 1,119 | 55 |
| 540 | 2,785 | 9,149 | 195 | 0.141 | 393 | 1,290 | 27 |
| 550 | 4,282 | 9,832 | 86 | 0.155 | 664 | 1,524 | 13 |
| 560 | 5,880 | 9,841 | 39 | 0.170 | 1,000 | 1,673 | 7 |
| 570 | 7,322 | 9,147 | 20 | 0.167 | 1,223 | 1,528 | 3 |
| 580 | 8,417 | 7,992 | 16 | 0.153 | 1,288 | 1,223 | 2 |
| 590 | 8,984 | 6,627 | 10 | 0.142 | 1,276 | 941 | 1 |
| 600 | 8,949 | 5,316 | 7 | 0.136 | 1,217 | 723 | 1 |
| 610 | 8,325 | 4,176 | 2 | 0.136 | 1,312 | 568 | 0 |
| 620 | 7,070 | 3,153 | 2 | 0.137 | 969 | 432 | |
| 630 | 5,309 | 2,190 | | 0.137 | 727 | 300 | |
| 640 | 3,693 | 1,443 | | 0.138 | 510 | 199 | |
| 650 | 2,349 | 886 | | 0.150 | 352 | 133 | |
| 660 | 1,361 | 504 | | 0.199 | 256 | 94 | |
| 670 | 708 | 259 | | 0.270 | 191 | 70 | |
| 680 | 369 | 134 | | 0.368 | 136 | 49 | |
| 690 | 171 | 62 | | 0.475 | 81 | 29 | |
| 700 | 82 | 29 | | 0.576 | 47 | 17 | |
| 710 | 39 | 14 | | 0.620 | 24 | 9 | |
| 720 | 19 | 6 | | 0.636 | 12 | 4 | |
| 730 | 8 | 3 | | 0.643 | 5 | 2 | |
| 740 | 4 | 2 | | 0.642 | 3 | 1 | |
| 750 | 2 | 1 | | 0.632 | 1 | 1 | |
| 760 | 1 | 1 | | 0.630 | 1 | 1 | |
| 770 | 1 | | | 0.600 | 1 | 0 | |
| | | | | Totals | 13,992 (X) | 14,790 (Y) | 13,228 (Z) |

NOTES:

$$\underline{1/} \quad X = \sum \bar{x}T, Y = \sum \bar{y}T, Z = \sum \bar{z}T$$

2/ Spectral transmittance, $T_c = Y/1,000 = 14.8$ percent

3/ Chromaticity coordinates:

$$x = X/(X + Y + Z) = 13,992/(13,992 + 14,790 + 13,228) = 0.3331$$

$$y = Y/(X + Y + Z) = 14,790/(13,992 + 14,790 + 13,228) = 0.3521$$

4/ Spectral transmittance, T_c , and chromaticity coordinates, x and y , for standard illuminant "C"

5/ The symbol "T" represents the transmittance, the ratio of transmitted to homogeneous radiant flux.

MIL-DTL-43511D

4.4.10 Ballistic resistance test. Ballistic resistance testing shall be in accordance with either method 1 or method 2 cited in paragraph 4.4.10.1 or 4.4.10.2. Method shall be as determined by the military service and specified in the applicable contract or purchase order.

4.4.10.1 Ballistic resistance test method 1 (for Army visors). The ballistic test at the V_0 point shall be conducted in accordance with MIL-STD-662 using a 0.22 caliber, 17 ± 0.5 grain, T37 shaped projectile with the following exceptions: electronic velocity detection devices (light beam or acoustic type) may be used to determine the velocity of the projectile, such devices placed no less than 8 inches and no more than 24 inches from the target; compressed gas propulsion of the projectile may be used. The sample shall be mounted on an Alderson 50th percentile male headform in the as worn position. The 0.002 inch thick aluminum foil witness sheet shall be mounted within 2 inches behind the area of impact. Three valid impacts shall be made on the lens; one in the center and one in each vision area. The sample shall be considered a failure if the aluminum foil witness sheet is punctured or if the sample is cracked. An impact shall be considered valid only if it meets any of the following:

- a. The impact velocity of the projectile is between 550 feet per second and 560 feet per second.
- b. The impact velocity of the projectile is less than 550 feet per second and the impact fails to meet the requirements in 3.5.10.
- c. The impact velocity of the projectile is more than 560 feet per second and the impact meets the requirements in 3.5.10.

4.4.10.2 Ballistic resistance test method 2 (for Air Force and Navy visors). The impact test shall be conducted in accordance with MIL-STD-662 and using a caliber .22 T37 fragment simulating projectile. The visor shall be rigidly mounted with the area to be impacted normal to the line of fire. An aluminum foil witness sheet, 2 mils thick, shall be mounted 2 inches behind the area of impact. Three valid impacts shall be made on the visor; one in the center and one in each vision area. An impact shall be considered valid only if it meets any of the following:

- a. The impact velocity of the projectile is between 550 feet per second and 560 feet per second.
- b. The impact velocity of the projectile is less than 550 feet per second and the impact fails to meet the requirements in 3.5.10.
- c. The impact velocity of the projectile is more than 560 feet per second and the impact meets the requirements in 3.5.10.

The visor containing the three valid impacts and the witness sheet shall be examined for conformance to the requirements in 3.5.10. Any penetration on the witness sheet shall be considered evidence of spall.

4.4.11 Abrasion resistance coating test. Before and after the abrasion tests, haze and luminous transmittance of the coated specimens and visors shall be calculated as specified in ASTM D 1003. The abrasion test, as specified in ASTM D 1044, using an abrasion of 500 cycles with a 500 gram load, shall be performed on flat panels which are coated by the same process as the visors. Additionally, visors shall be tested using the eraser test. The eraser test shall be performed by rubbing with a specially standardized eraser mounted as illustrated on figure 5 and held approximately normal to the visor. The device and eraser material indicated on figure 5 shall be used for this test. The areas of the visor where the eraser test is to be performed shall be identified and shall include at least three areas in the critical area of vision. The eraser shall be rubbed across the surface of the coated visor from one point to another, over the same path, for 20 complete cycles (motion of the eraser up and back is one cycle) with a force of 2.0 to 2.5 pounds continuously applied. Wherever possible, rubs of about 1 inch length are preferred. After the rubbing has been completed, the lens shall be thoroughly cleaned to remove dirt, film, finger marks and grease marks using a mild detergent and water followed by drying with a soft cloth or lens tissue. The visor shall meet the requirements in 3.5.11.

MIL-DTL-43511D

4.4.12 Bayer abrasion resistance. The visor / or 6 curve lenses shall be tested using the oscillating sand method. The abrasion test will be performed in accordance with ASTM F 735 using 500 grams Alundum® Norton ZF #12 (Saint-Cobain) for 600 cycles. A CR-39 reference lens or equivalent of same diopter will be tested in parallel to the coated specimen. The resulting ratio will be the change in haze, tested using ASTM D 1003, of the reference specimen divided by the change in haze of the coated specimen.

4.4.13 Coating adhesion. The tape test adhesion shall be performed using ASTM D 3359. The coated visor shall be subject to a crosshatch (cross hatch cutter with a 1.0 mm spacing) and then subject to 3 consecutive tape pulls. A tape having an adhesion to steel of 45-55 oz per inch shall be applied to the cross hatched area and firmly pressed down. Tape shall be cut to a length of approximately three inches long and firmly applied to the visor. To ensure good contact with the visor, rub the tape firmly with an eraser. Within 90 ± 30 seconds of application, remove the tape by seizing the free end and rapidly (not jerked) back upon itself at as close to an angle of 180° as possible. This adhesion test shall be repeated after the visor is subjected to the humidity test, as specified in MIL-STD-810, Method 507, Procedure III, for 120 hours (5 cycles).

4.4.14 Weathering resistance. Visors shall be exposed in a weatherometer in accordance with MIL-STD-810, method 505.3, procedure II. For visors which contain external coatings, the coating adhesion test shall be performed after weather resistance tests have been completed.

4.4.15 Chemical resistance. The visors shall be exposed to the following chemicals:

- a. Insect repellent, controlled release (DEET)
- b. JP4 aircraft turbine fuel
- c. JP8 aircraft turbine fuel, kerosene type
- d. Aircraft lube oil, turbine engine, synthetic base
- e. Aircraft hydraulic fluid, fire-resistant, synthetic base
- f. Degreasing solvent, type I (mineral spirits)
- g. Cleaning compound, turbine engine gas path, 20 % solution

The chemical exposure will be tested for a 10 hour period at ambient room temperature conditions. The chemicals shall be contained by sealing an o-ring (0.5 inch or 0.75 inch diameter) to either the concave or convex surface of the visor. At the end of the test, the surface shall be thoroughly cleaned using a mild detergent and water followed by drying with a soft cloth or lens tissue. The visor shall then be visually inspected for visible damage and shall pass the requirements of 3.5.3 and 3.5.6 ensuring the same areas that were exposed to the chemicals are tested for these requirements. The haze and transmittance shall be measured before and after the exposure to the chemicals. Each visor shall have two (2) locations tested for each chemical type (i.e. left and right side of the visor).

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

MIL-DTL-43511D

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The class 1, class 2, and class 3 visors are intended to be used on flight helmets used by aircrew personnel.

6.2 Acquisition requirements. Acquisition documents should specify the following:

- a. Title, number and date of this specification.
- b. Class of visor required (see 1.2)
- c. Issue of DODISS to be cited in the solicitation and, if required, the specific issue of individual documents referenced (see 2.2.1 and 2.3)
- d. When first article is required (see 3.1)
- e. When abrasion resistant coating is required (see 3.5.11)
- f. Packaging requirements (see 5.1).

6.3 First article. When a first article is required, it will be inspected and approved under the appropriate provisions of FAR 52.209. The first article should be a preproduction sample. The contracting officer should specify the appropriate type of first article and the number of units to be furnished. The contracting officer should also include specific instructions in acquisition documents regarding arrangements for selection, inspection, and approval of the first article.

6.4 Coatings. All requirements for abrasion resisting coatings applied to polycarbonate visors are included in this document.

6.5 Luminous transmittance. For the purpose of this specification, luminous transmittance is defined as the ratio of the luminous flux transmitted by the visor to the luminous flux incident on the visor. It is measured with a sensor corrected to compare with the photopic sensitivity of the human eye without regard to specific wavelengths. ASTM D 1003 or a specified modification thereof is a way of determining luminous transmittance. A CIE C source (average daylight) is used to make the luminous transmittance measurements.

6.6 Spectral transmittance. For the purpose of this specification, spectral transmittance is defined as radiant transmittance evaluated for a specific range of wavelengths of incident energy. It is desirable that it be measured with an automatic recording spectrophotometer of the required range of sensitivity and evaluated according to the applicable instructions.

6.7 Suggested source of supply. Navy has determined that Gentex Corporation is an acceptable source for visors meeting the requirements stated in this document.

6.8 Subject term (key word) listing

Aircrew personnel
Armor
Eye protection
Flight
Shield

6.9 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

MIL-DTL-43511D



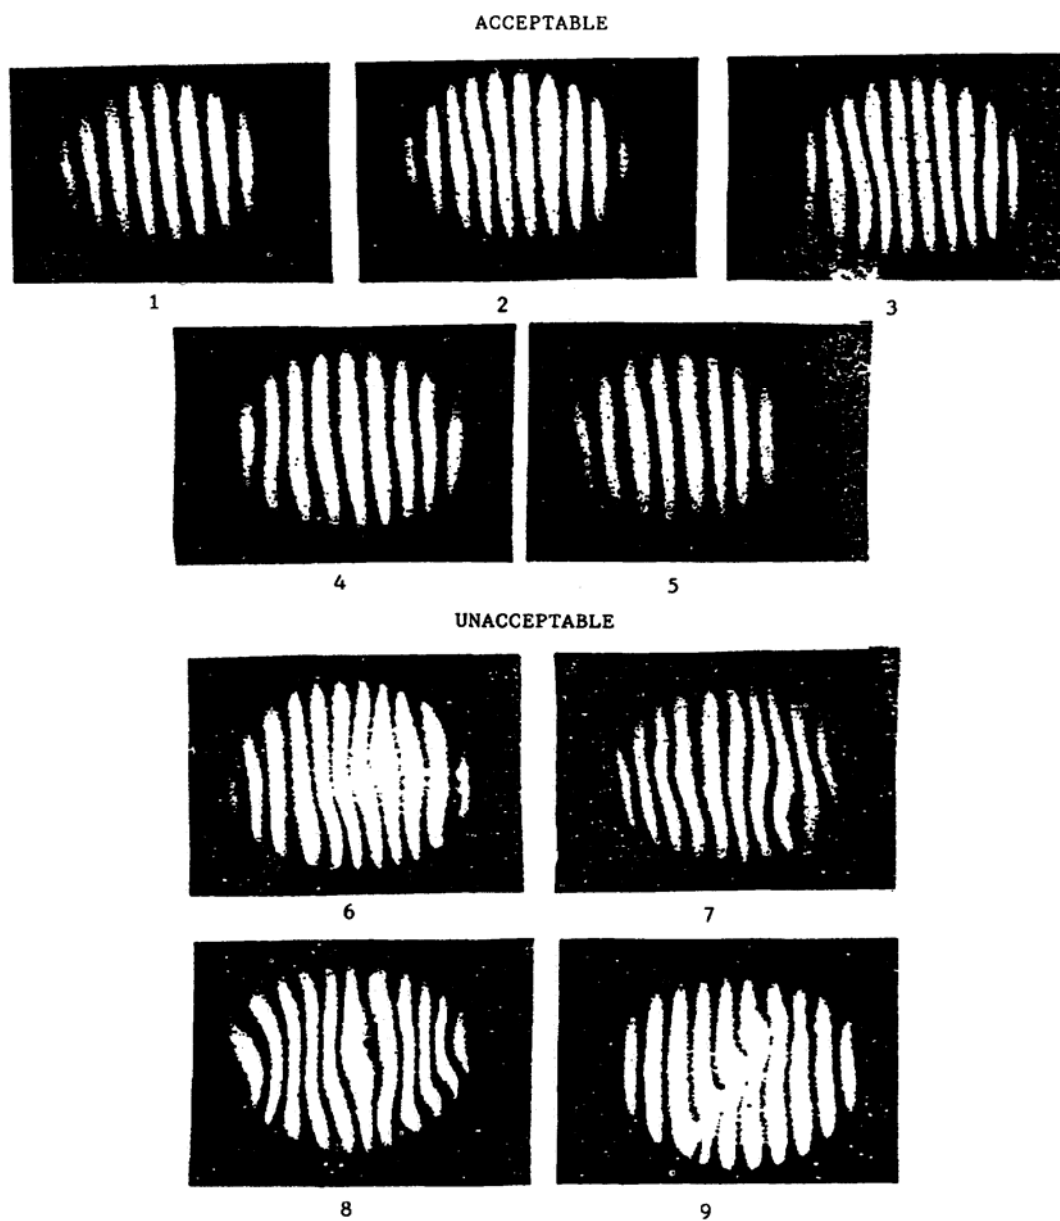


FIGURE 2. Visors optical distortion standards.

MIL-DTL-43511D

FIGURE 3. Chromaticity coordinates.

MIL-DTL-43511D

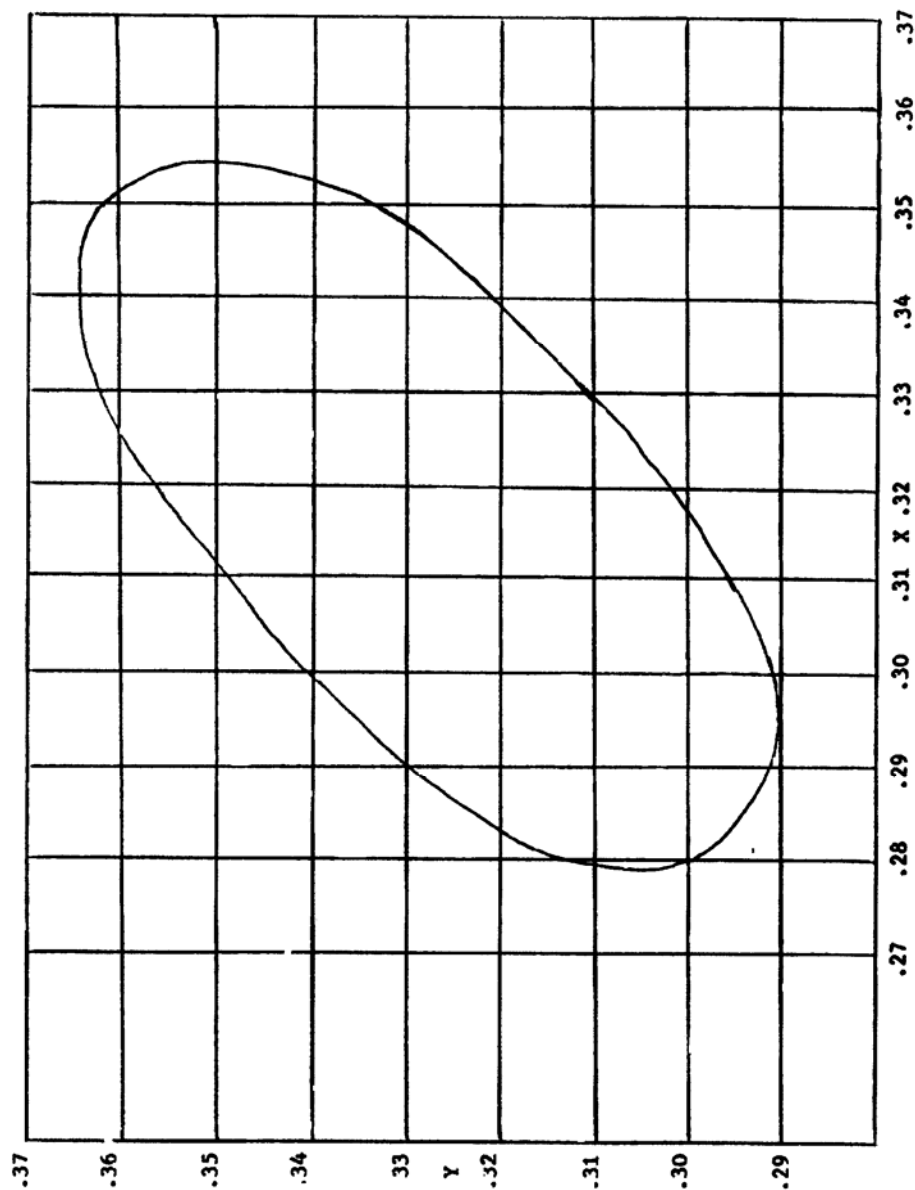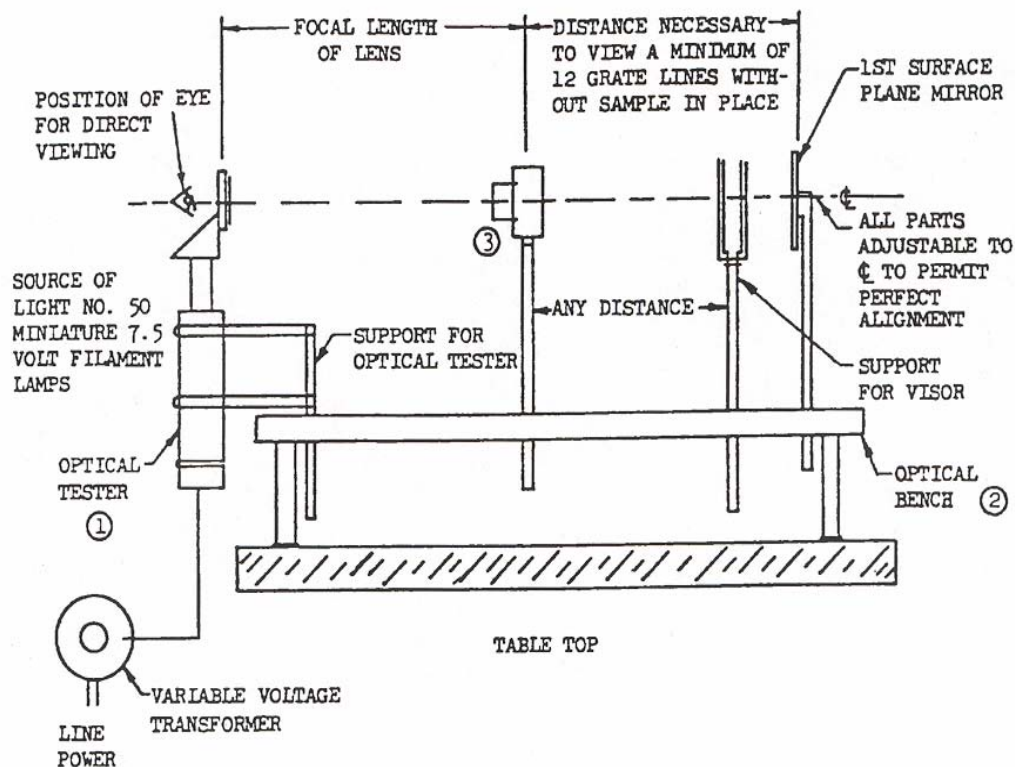

1 MODEL "B" OR EQUIVALENT OPTICAL TESTER WITH A 50 to 60-LINE GRATING, WITH OPTICAL BENCH ADAPTER OR EQUIVALENT.

2 THE COMPLETE TEST ASSEMBLY, OR COMPONENTS, DEPICTED IN THIS FIGURE MAY BE OBTAINED AS THE MODEL E DISTORTION TESTER FROM DATA OPTICS INC., 115 HOLMES ROAD, YPSILANTI, MICHIGAN 48198-3020, PHONE 800-321-9026 OR 734-483-8288.

FIGURE 4. Distortion tester.

MIL-DTL-43511D

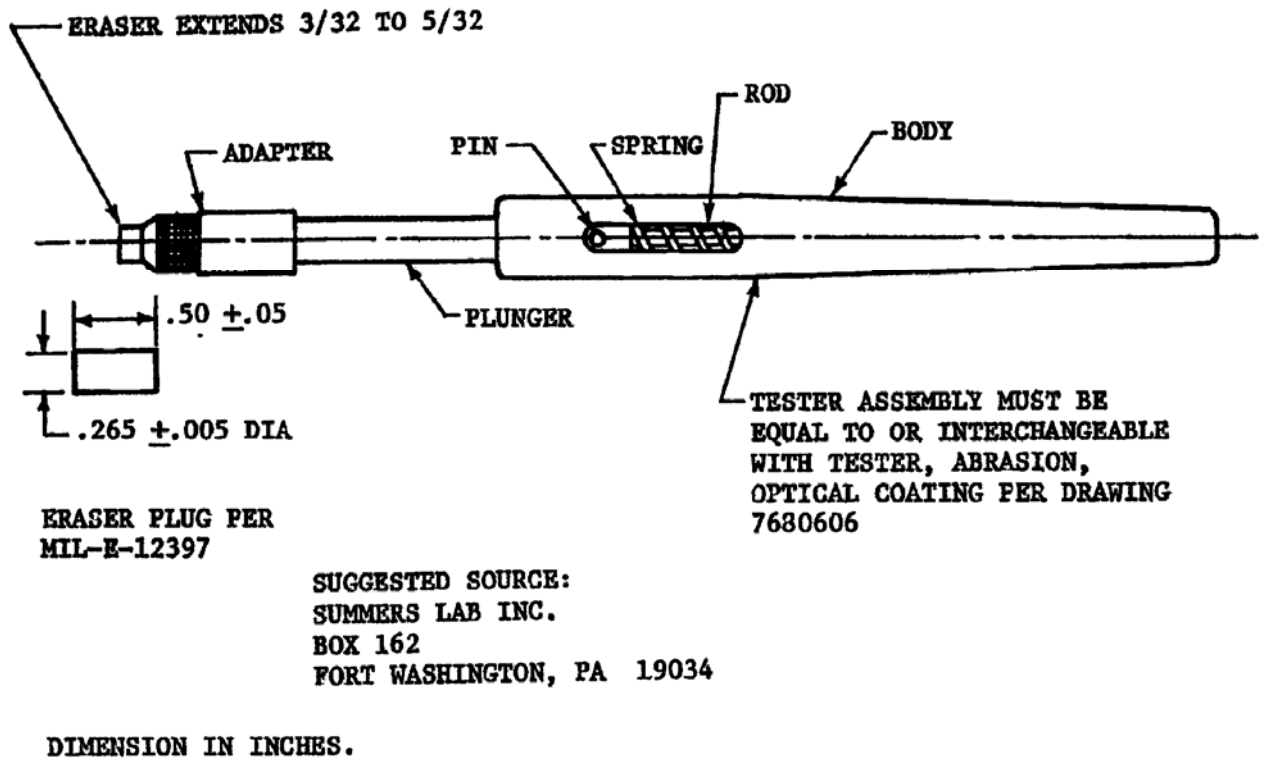


FIGURE 5. Eraser abrasion tester assembly and eraser plug.

MIL-DTL-43511D

Custodians:

Army - GL

Air Force – 11

Navy - AS

Preparing activity:

DLA - CT

(Project 8415-0183)

Review activities:

Army – MD, AV

Navy - NU

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST online database at <http://assist.daps.dla.mil>