

MIL-F-7190B
16 December 1985
SUPERSEDING
MIL-F-7190A
17 August 1956

MILITARY SPECIFICATION

FORGINGS, STEEL, FOR AIRCRAFT/AEROSPACE EQUIPMENT AND SPECIAL ORDNANCE APPLICATIONS

1. SCOPE

1.1 Scope. This specification covers steel forgings suitable for use in the construction of aircraft/aerospace equipment, special ordnance, and related accessories.

1.2 Classification. Steel forgings shall be furnished in the following grades. If grade is not specified, then Grade A is required (see Table I and 6.2.1).

Grade A - Testing and inspection
Grade B - Testing and inspection
Grade C - Testing and inspection

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. Unless otherwise specified, the following specifications and standards of the issue listed in that issue of the Department of Defense Index of Specification and Standards (DODISS) specified in the solicitation form a part of this specification to the extent specified herein.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: AFWAL/MLSE, ATTN: Standardization Manager, Wright-Patterson AFB, OH 45433 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AREA FORG

AMSC N/A

DISTRIBUTION STATEMENT A. Approved for public release; distribution unlimited.

MIL-F-7190B

SPECIFICATIONS

MILITARY

MIL-H-6875 Heat Treatment of steels (Aircraft Practice),
Process for

STANDARDS

FEDERAL

FED-STD-151 Metals, Test Methods

MILITARY

MIL-STD-163 Steel Mill Products, Preparation for Shipment and
Storage

MIL-STD-183 Continuous Identification Marking of Iron and Steel
Products

MIL-STD-1949 Inspection Process, Magnetic Particle

MIL-STD-6866 Inspection, Penetrant Method of

(Copies of specifications, standards, handbooks, drawings, and publications required by manufacturers in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)

2.2 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence.

3. REQUIREMENTS

3.1 Materials. Forgings shall be produced from cast ingots or from a wrought stock conforming to the requirements of the applicable material specification and applicable drawing, as specified by the contract or purchase order. Materials shall be worked prior to and during the forging operation to produce a wrought metallurgical structure.

3.1.1 Cleanliness. Cleanliness rating requirements shall be as required by the material specification or as agreed upon between the purchaser and contractor.

3.1.2 Mill heat identification. Material to be used in all forgings shall be identified by mill heats within each ingot when required by the purchaser.

MIL-F-7190B

3.1.2.1 Alloy steel and corrosion resistant steel. For forgings of alloy steel and corrosion resistant steel, each bar, billet, bloom, or forging multiple received from the mill shall be marked with the mill heat number. Bar less than 0.500 inches in diameter or width shall be securely bundled and identified with a durable tag marked with the purchase order, specification number and/or grade, heat number, nominal size and manufacturer's identification. The tag shall be attached to each bundle. As an alternative, the manufacturer may box the bars and mark the box with the same identification as listed for bundles.

3.1.2.2 The mill heat number or an appropriate code, as agreed upon by purchaser, shall appear on individual forgings and all certification pertaining to these forgings.

3.1.3 Forging stock specification. Forge shop shall determine that the forging stock conforms to the requirements of the applicable material specification. Forging shop shall obtain complete test reports from the mill on each heat of forging stock.

3.2 Forging process. Forgings shall be formed to the specified configuration and dimensions. Sufficient working shall be applied to the material to provide the specified grain size and a wrought structure throughout the forging.

3.2.1 Forging procedures. Forger shall establish forging sequence and other processing procedures, such as heat treating and cleaning, suitable for producing high quality forgings. These procedures shall be documented on operation sheets for the purpose of maintaining consistent practices and shall not be changed without the specific approval and consent of the purchaser.

3.2.2 Heat equipment control. Forging furnaces shall be instrumented to control and record temperature variations in accordance with MIL-H-6875.

3.2.3 Forging flow pattern control. The forging techniques employed shall produce, except in the area of die forging parting plane which contains end grains, an internal grain flow pattern such that it shall essentially conform to the structural shape of the part and shall be free from both reentrant and sharply folded flow lines.

3.2.3.1 First article forging. Sections taken from a test forging at locations designated on the applicable drawing shall be suitably prepared and etched to reveal the grain flow developed in the forging. When the specified alloy is not conducive to good grain flow determination, a suitable alloy exhibiting good grain flow etch response and having equivalent forgeability may be substituted. The grain flow pattern shall be

MIL-F-7190B

in essential agreement with the drawing or shall be as agreed upon by the purchaser and vendor and as provided in 3.2.3. This procedure shall be repeated following any major change in forging technique or die design. When the test forging is of the same alloy as specified, the sections may also be used for metallographic examination and hardness surveys. Photographs of each section of adequate quality and magnification to resolve detailed main flow-pattern shall be furnished to the purchaser and one set shall be retained by the forger.

3.2.4 Welding. Repair welding shall not be permitted, except as indicated on applicable drawings and approved by the procuring activity.

3.2.5 Cleaning. All forgings shall be thoroughly cleaned by tumbling, machining, shot, grit or sand blasting, pickling, or other process approved by the purchaser. Local surface imperfections may be removed by blending to the adjacent as-forged surface provided all drawing requirements are met. For parts which will be subjected to penetrant method of nondestructive testing, concurrence of the purchaser is required when the cleaning method does not include etching.

3.3 Heat treatment. Forgings shall be heat treated in accordance with MIL-H-6875 to produce the condition and properties specified, unless the purchaser issues instructions modifying this requirement. When heat treatment is not specified, carbon and alloy steel forgings shall be furnished in the normalized or normalized and tempered condition and corrosion and heat resistant steel forgings shall be furnished in the solution heat treated or annealed condition.

3.3.1 Heat treatment shall be performed on the entire forging, not on a localized section.

3.3.2 All forgings shall be cleaned of contaminants before heat treatment.

3.4 Heat treatment records. The forger shall keep records of all furnace charts for each heat treat batch or cycle. Unless otherwise specified, records shall be kept on file for a minimum of five years. Information retained shall include set temperature, time, and furnace loading instructions.

3.5 Metallographic structure. The microstructure of the finished forging shall be essentially uniform and free from defects, and shall be free from indications of overheating or burning.

3.6 Quality. Forgings shall be ordered to the grades specified in Table 1, and shall be subjected to the tests as indicated therein. Tests shall be conducted in accordance with the methods in 4.3.

MIL-F-7190B

TABLE I. Required tests for forgings.

Grade	Tensile ^{1/}	Hardness	Magnetic particle or fluorescent penetrant	Grain flow	Composition
A	X	X	X	X	X
B	X	X	---	---	X
C	---	X	X	---	X

^{1/} Tensile tests required only for forgings furnished in the final heat treated condition. The frequency of testing shall be as required by Table II.

3.7 Hardness. Hardness of the forgings shall be specified by the purchaser (see 6.2).

3.8 Nondestructive inspection. Unless otherwise specified, forgings shall be inspected by nondestructive methods as required in Table I based on specified forging grade (see 4.3.4). The purchaser shall specify the acceptance criteria.

3.9 Dimensions and tolerances. Dimensions and tolerances shall be as specified on the applicable drawing or purchase documents.

3.10 Identification of product. Forgings shall be individually marked in accordance with MIL-STD-183, including the serial number when required.

3.11 Workmanship. Forgings shall be uniform in quality and condition, and shall be free from tears, cracks, seams, laps, internal ruptures, imbedded scale, segregation, or other defects which may detrimentally affect the suitability for the purpose intended.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the forger is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the forger may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the purchaser. The purchaser reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

MIL-F-7190B

4.2 Classification of inspections.

4.2.1 Results of all tests and location of test specimens shall be reported to the purchaser.

4.2.2 Instructions issued by the purchaser requiring more stringent quality conformance sampling procedures shall take precedence over the requirements of this specification.

4.2.3 Tests for properties of a given heat, as required by the applicable material specification, need not be repeated on forgings from the heat provided that these tests have been performed on the forging stock, heat identity of the forgings is maintained as required by 3.1.2, and reports of tests conducted are available.

4.3 Test methods and specimen preparation. Test specimens shall be prepared and tested in accordance with the applicable methods of FED-STD-151. The frequency of sampling and testing shall be as specified in Table II, based on specified forging grade.

TABLE II. Quality conformance inspection.

Tests and inspections	Requirement	Test method	Sampling and testing frequency
Composition	3.6	4.3	Each mill heat
Cleaning	3.2.5	Visual	Each forging
Metallographic structure	3.5	4.3.1	One forging from the first lot of each configuration: Grade A
Hardness	3.7	4.3.	See 4.3.3
Grain flow	3.2.3, 3.2.3.1	4.3.1	One forging from the first lot of each configuration: Grade A
Heat identification	3.1.2.2	Visual	Each applicable forging
Nondestructive inspection	3.8	4.3.4	Each forging for Grades A & C
Tensile Properties	3.6	4.3	One sample per lot for Grades A & B

MIL-F-7190B

4.3.1 Metallographic structure. Grain size determinations, grain flow pattern, and other metallographic examinations shall be made in accordance with FED-STD-151.

4.3.2 Mechanical properties. Unless otherwise specified, when tensile testing of a forging is required the tensile test specimens shall be taken from the locations in the forgings as specified by the purchaser. When there is an agreement between forger and purchaser not to destroy a forging because of excessive cost or forging size, test specimens shall be taken from a full size prolongation of the forging in the area of maximum section reduction. The direction for testing shall be as specified by the purchaser. Variations from properties because the section size, or test specimen orientation, shall require the approval of the purchaser.

4.3.2.1 Varieties in properties prolongations shall not be parted from the forgings until all required thermal treatments required to be performed by the forger have been completed.

4.3.2.2 When it is not practicable to take a specimen from a forging or from a prolongation, a representative test bar may be used when agreed upon between purchaser and forge shop. The representative test bar shall be from the same heat of material as the forgings and shall have been heat treated with the parts. The percent reduction given the representative test bar shall not be greater than the minimum amount of reduction given the forging.

4.3.2.3 When parts are made in multiple from a single forging, i.e., forged in one piece and machined apart, tests on the large single forging shall govern the individual units.

4.3.3 Hardness. Forgings shall be sampled for hardness tests in accordance with Table III.

TABLE III. Hardness test sampling requirements.

Condition	Quantity ^{1/}	Sample size
Thermal treatment other than final heat treatment.	1 - 20	All
	21 - 100	25% (20 pcs. min.)
	Over 100	10% (25 pcs. min.)
Final heat treatment	1 - 44	All
	45 - 65	44
	66 - 110	60
	111 - 180	67
	181 - 300	73
	301 - 500	78
	501 - 800	80
	Over 800	10% (85 pcs. min.)

^{1/} In each heat treat lot of same forging lot.

MIL-F-7190B

4.3.4 Nondestructive inspection. Each Grade A and C forging shall be magnetic particle inspected in accordance with MIL-STD-1949 to determine conformance with the workmanship requirement herein. When the magnetic characteristics of the material prevent satisfactory magnetic particle inspection, the forgings shall be fluorescent penetrant inspected in accordance with MIL-STD-6866. Standards for acceptance and rejection shall conform to the workmanship requirements herein, unless established by the purchaser, and are subject to the approval of the purchaser.

4.3.4.1 The forger shall maintain records of nondestructive testing of Grade A & C forgings for a period of time agreed upon by the purchaser and vendor.

4.4 Maintenance of facilities. The forger shall keep records demonstrating that the facilities used for heat treatment to control, measure, and test the forgings during processing and inspection are properly maintained and are checked at stated intervals against acceptable standards for accuracy. Heat treatment controls shall be made in accordance with Specification MIL-H-6875.

4.5 Nonconforming items. Failure of any valid specimen to conform to specified requirements shall cause the forgings represented by such specimens to be subject to rejection. When a failed specimen is judged to be invalid, either dimensionally or for equipment malfunction, replacement from a location adjacent to the original specimen shall be allowed. Forger, in an attempt to obtain a waiver for parts represented by a valid specimen failure, may retest two specimens removed from a location adjacent to the nonconforming specimen. If these specimens fail and are valid, then individual forgings in the lot may be tested (100 percent testing of the lot represented by the failed test).

4.5.1 Upon completion of the additional testing, forger shall submit for review by the purchaser all data pertaining to the nonconforming parts. Data shall be submitted in the format given by the purchaser and shall include:

- a. identification of nonconforming items
- b. number of pieces involved
- c. all original test results
- d. all results of retest
- e. reason for nonconformance, if known
- f. corrective action taken to prevent recurrence of nonconformance.

MIL-F-7190B

4.5.2 Forger shall not ship any nonconforming forgings until notified by the purchaser that the forgings in question are acceptable for the application intended.

4.5.3 Rejection. Forgings not conforming to this specification or to authorized modifications will be subject to rejection.

5. PACKAGING

5.1 Application. The requirements of this section apply only to direct purchases by or direct shipment to the Government.

5.2 Preservation and packaging. Forgings shall be prepared for shipment in accordance with MIL-STD-163. Packaging requirements for forgings purchased by non-government sources shall be established by agreement between the purchaser and the vendor.

5.3 Marking. Interior packages and exterior shipping containers shall be marked in accordance with the requirements of MIL-STD-163. The identification shall be composed of the following information listed in the order shown:

Stock No. or other identification number as specified in the purchase documents*
 FORGINGS, STEEL
 Specification MIL-F-7190B
 Grade
 Part No.
 Steel Composition Designation
 Heat Treat Condition
 Quantity contained
 Contract or Order No.
 Manufacturer's name or trade mark
 Gross weight

*NOTE: The forger shall enter the National Stock No. specified in the purchase document or as furnished by the purchaser. When the National Stock No. is not provided or available from the purchaser, enter the Stock No. or other identification as provided by the purchaser.

6. NOTES

6.1 Intended use. This specification covers all types of rough steel forgings for aircraft and special ordnance applications. Additional machining operations will be required in almost all cases before the forgings are suitable for use.

MIL-F-7190B

6.2 Ordering data.

6.2.1 Procurement documents should specify the following:

- a. Title, number revision letter, and date of this specification
- b. Grade
- c. Part no.
- d. Material composition.
- e. Type of packing required.

6.2.2 Applicable drawings should specify:

- a. Part no.
- b. Specification number/letter.
- c. The material composition and applicable material specification for the steel to be used.
- d. Required mechanical properties or heat treatment (tensile, hardness, or other applicable material specification requirement to be applicable).
- e. Any grain flow pattern, grain size, or other metallographic requirement.
- f. Nondestructive testing requirement other than shown in Table I.
- g. Dimensions and tolerances.
- h. Traceability requirements, if applicable.

6.3 Definitions.

6.3.1 Forging lot. A forging lot shall include all forgings of the same design produced from the same heat of steel and forged to shape in any one production forging run, normally in any one day, and presented for inspection at one time.

6.3.2 Forging heat treat batch. All forgings of the same alloy are heat treated in the same furnace without interruption. Different forging designs may be mixed in the furnace provided section thicknesses are equivalent.

MIL-F-7190B

6.4 Marginal indicia. The margins of this specification revision have not been marked to indicate additions, changes or deletions from the previous issue due to the extensive nature of all changes. Reviewers are cautioned to evaluate the specifications as a whole in relation to the previous issue.

Custodians:

Air Force - 20
Army - AL
Navy - AS

Preparing Activity:

Air Force - 20
Project No.: FORG-0090

Review Activity:

Navy - OS

User Activity:

Army - MR

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge (*DO NOT STAPLE*), and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

★ U.S. Government Printing Office: 1982-388-879/5894

(Fold along this line)

(Fold along this line)




NO POSTAGE
NECESSARY
IF MAILED
IN THE
UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE \$300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 73236 WASH DC

POSTAGE WILL BE PAID BY HQ U.S. AIR FORCE

AFWAL/MLSE
ATTN: Standardization Manager
Wright-Patterson AFB OH 45433-6533

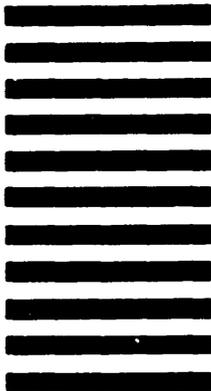

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER MIL-F-7190B		2. DOCUMENT TITLE Forgings, Steel, for Aircraft/Aerospace Equipment and Special Ordnance Applications	
3a. NAME OF SUBMITTING ORGANIZATION		4. TYPE OF ORGANIZATION <i>(Mark one)</i>	
b. ADDRESS <i>(Street, City, State, ZIP Code)</i>		<input type="checkbox"/> VENDOR	
		<input type="checkbox"/> USER	
		<input type="checkbox"/> MANUFACTURER	
		<input type="checkbox"/> OTHER <i>(Specify):</i> _____	
5. PROBLEM AREAS			
a. Paragraph Number and Wording:			
b. Recommended Wording:			
c. Reason/Rationale for Recommendation:			
6. REMARKS			
7a. NAME OF SUBMITTER <i>(Last, First, MI)</i> – Optional		b. WORK TELEPHONE NUMBER <i>(Include Area Code)</i> – Optional	
c. MAILING ADDRESS <i>(Street, City, State, ZIP Code)</i> – Optional		8. DATE OF SUBMISSION (YYMMDD)	

(TO DETACH THIS FORM, CUT ALONG THIS LINE.)