

MIL-S-85848/2(AS)

1 May 1987

MILITARY SPECIFICATION SHEET

SLEEVING, FOR IDENTIFICATION MARKING, HEAT SHRINKABLE,
POLYVINYLIDENE FLUORIDE, FLEXIBLE

This specification is approved for use within the Naval Air Systems Command, Department of the Navy, and is available for use by all Departments and Agencies of the Department of Defense.

The complete requirements for procuring the sleeving described herein shall consist of this document and the issue in effect of MIL-S-85848(AS).

REQUIREMENTS:


Continuous operating temperature range: Type I: -40°C to $+150^{\circ}\text{C}$ (-40°F to $+302^{\circ}\text{F}$)
Type II: -55°C to $+175^{\circ}\text{C}$ (-67°F to $+347^{\circ}\text{F}$)

Classification: The heat shrinkable identification sleeving shall be furnished in the following types, as specified:

Type I - Flatweb format
Type II - Sleeving format

Color: The standard color shall be white. Other colors are available. All colors shall conform to the requirements of Class 1 of MIL-STD-104.

Military Part Number: The Military Part Number shall consist of the basic number of this specification sheet and dash numbers as shown below:

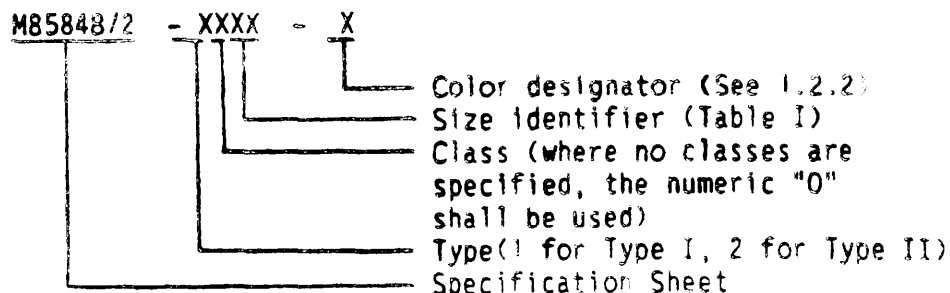

Part number example: White, type II, .187 as supplied diameter, 1.62 inch length shall be identified as: M85848/2-2004-9.

AMSC N/A

FSC 5970

DISTRIBUTION STATEMENT A, Approved for public release; distribution is unlimited.

MIL-S-85848/2(AS)

TABLE I - CONSTRUCTION DETAILS FOR TYPE I FLATWEB (Inches)

MILITARY PART NUMBER	W WIDTH AS SUPPLIED	L LENGTH AS SUPPLIED	RANGE OF WIRE DIAMETER	MIN. # OF SLEEVES ROLL FORM PACKAGE	MIN. # OF SLEEVES FROM 1 FT LENGTH
-1001-*	.250 \pm .03	1.000 \pm .03	.040 - .080	5000	192
-1002-*	.333 \pm .03	1.000 \pm .03	.080 - .130	5000	144
-1003-*	.375 \pm .03	1.000 \pm .03	.130 - .160	5000	128
-1004-*	.500 \pm .03	1.000 \pm .03	.160 - .235	5000	96
-1005-*	.625 \pm .03	1.000 \pm .03	.235 - .290	5000	76
-1006-*	.750 \pm .03	1.000 \pm .03	.290 - .390	3000	64
-1007-*	.250 \pm .03	2.000 \pm .03	.040 - .080	2500	96
-1008-*	.333 \pm .03	2.000 \pm .03	.080 - .130	2500	72
-1009-*	.375 \pm .03	2.000 \pm .03	.130 - .160	2500	64

* The asterisk in the part number shall be replaced by color code designations.

Table II Construction Details for Type II Sleeving (inch)

MILITARY PART NUMBER	DIAMETER AS SUPPLIED MIN	DIAMETER AFTER RECOVERY MAX.	LENGTH AS SUPPLIED	MINIMUM MARKING LENGTH	RANGE OF WIRE DIAMETER	NUMBER OF SLEEVES/UNIT PACKAGE, MIN
-2001-*	.093	.031	1.65 \pm .05	1.5	.050-.085	5000
-2002-*	.125	.062	1.65 \pm .05	1.5	.075-.115	5000
-2003-*	.125	.046	1.66 \pm .08	1.5	.050-.115	5000
-2004-*	.187	.093	1.62 \pm .05	1.5	.100-.165	2500
-2005-*	.187	.062	1.66 \pm .05	1.5	.050-.165	2500
-2006-*	.250	.125	1.60 \pm .05	1.5	.135-.235	2500
-2007-*	.250	.093	1.61 \pm .08	1.5	.100-.235	2500
-2008-*	.375	.187	1.59 \pm .08	1.5	.200-.355	1500
-2009-*	.375	.125	1.80 \pm .08	1.5	.135-.355	1500
-2010-*	.475	.250	1.73 \pm .13	1.5	.260-.450	1000
-2011-*	.093	.046	1.89 \pm .05	1.75	.050-.085	5000
-2012-*	.125	.062	1.89 \pm .05	1.75	.075-.115	5000
-2013-*	.125	.046	1.89 \pm .08	1.75	.050-.115	5000
-2014-*	.187	.093	1.88 \pm .08	1.75	.100-.165	2500
-2015-*	.187	.062	1.89 \pm .05	1.75	.050-.165	2500
-2016-*	.250	.125	1.85 \pm .05	1.75	.135-.235	2500
-2017-*	.250	.093	1.84 \pm .08	1.75	.100-.235	2500
-2018-*	.375	.187	1.84 \pm .08	1.75	.200-.355	1500

* The asterisk in the part number shall be replaced by color code designations(see 1.3 of MIL-S-85848(AS)).

MTL-S-85848/2(AS)

TABLE III - PHYSICAL PROPERTIES 1/

PROPERTY	REQUIREMENT	TEST PROCEDURE AND CONDITIONS
Dimensions	Pass	4.6.2
Fungus resistance	Rating of 1 or less	4.6.1, ASTM G21
Specific Gravity, Max	2.0	4.6.1, ASTM D792
Water absorption, %, max.	0.5	4.6.1, ASTM D570, 24 hrs @ 23°C(73°F)
Color stability	Pass	4.6.4, 24 hrs @ 149° ±1°C(300°±2°F)
Tensile strength, psi, min	5000	4.6.5 ASTM D882, Speed D
Secant Modulus, psi, min	80,000	4.6.6.1. ASTM D882, 2% strain
Heat shock	No cracks, flowing or dripping 2/	4.6.7, Type I: 177° ±1°C(330°±2°F) Type II: 300°±3°C(573°±7°F)
Heat resistance Print performance	No cracking 2/ Pass	4.6.8, Type I 150° ±2°C(302°±4°F) Type II 180°±2°C(356°±4°F) for 168 hours.
Low temperature flexibility	No cracking 2/	4.6.9, Type I: -40° ±1°C(-40°±2°F) Type II: -55°±1°C(-67°±2°F)
Fluid resistance Tensile strength, after psi, min Print performance	4000 Pass	4.6.10
Flammability	Pass	4.6.11.3
Vacuum outgassing	TML less than 1% CVCM less than 0.1%	4.6.12
Print performance	Pass	4.6.13

1/ Unless otherwise specified, the stated requirement, test conditions, and procedures are for all types.

2/ The degree of bend shall be 90° up to 0.375 inch sleeve width or diameter. All others shall be bent through 45°.

MIL-S-85848/2(AS)

Restricted Shrinkage: Test method 4.5.3. Type I: $204^{\circ}\pm 2^{\circ}\text{C}$ ($400^{\circ}\pm 4^{\circ}\text{F}$);
Type II: $175^{\circ}\pm 2^{\circ}\text{C}$ ($347^{\circ}\pm 4^{\circ}\text{F}$) until the sleeve is snug around the wire.

Unrestricted shrinkage: Test method 4.5.2. $200^{\circ}\pm 2^{\circ}\text{C}$ ($392^{\circ}\pm 4^{\circ}\text{F}$) for 5 minutes.

Shelf life conditions: Supplier shall certify to storage at ambient storage conditions for two years followed by conformance to the construction details of either Table I or II.

Shelf life extension: Test method 4.6.13

Intended Use: Heat shrinkable flexible polyvinylidene fluoride identification sleeving is used as a snug fitting non-insulating identifier to mark wires, wire bundles, cables and cable harnesses.

Preparing Activity:
Navy AS
Project No. 5970-N664-2)