

MIL-S-8660C  
 22 September 1983  
 SUPERSEDING  
 MIL-S-8660B  
 30 October 1963

## MILITARY SPECIFICATION

### SILICONE COMPOUND, NATO CODE NUMBER S-736

This specification is approved for use by all Departments and Agencies of the Department of Defense.

#### 1. SCOPE

1.1 Scope. This specification covers one type of a nonmelting, heat stable silicone compound for use in high tension electrical connections, ignition systems and electronics equipment; for application to unpainted mating threaded or non-threaded surfaces, and as a lubricant for components fabricated from rubber. This compound is effective in the temperature range from -54°C (-65°F) to +204°C (+400°F) for extended periods and to 260°C (500°F) for short periods. This compound is identified by NATO symbol S-736 (see 6.5).

#### 2. APPLICABLE DOCUMENTS

##### 2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. Unless otherwise specified, the following specifications, standards, and handbooks of the issue listed in that issue of the Department of Defense Index of Specifications and Standards (DoDISS) specified in the solicitation form a part of this specification to the extent specified herein.

#### SPECIFICATIONS

##### FEDERAL

O-A-548	-	Antifreeze/Coolant, Engine, Ethylene Glycol, Inhibited, Concentrated.
O-G-491	-	Glycerol, Technical (High Gravity).
QQ-A-250/4	-	Aluminum Alloy 2024, Plate and Sheet.
QQ-B-613	-	Brass, Leaded and Non-Leaded, Flat Products, (Plate, Bar, Sheet and Strip).
QQ-C-502	-	Copper Rods and Shapes, and Flat Products with Finished Edges (Flat Wire, Strips and Bars).

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Engineering Specifications and Standards Department (Code 93), Naval Air Engineering Center, Lakehurst, NJ 08733, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

FSC 6850

## MIL-S-8660C

- QQ-L-201 - Lead Sheet.
- QQ-P-416 - Plating, Cadmium (Electrodeposited).
- QQ-S-571 - Solder, Tin Alloy, Lead-Tin Alloy, and Lead Alloy.
- QQ-Z-301 - Zinc Sheet and Strip.
- TT-I-735 - Isopropyl Alcohol.

## MILITARY

- MIL-M-14 - Molding Plastics and Molded Plastic Parts, Thermosetting.
- MIL-E-463 - Ethyl Alcohol (For Ordnance Use).
- MIL-E-480 - Enamel, Baking, Phenol-or-Urea-Formaldehyde.
- MIL-I-631 - Insulation, Electrical, Synthetic-Resin Composition, Non-rigid.
- MIL-R-3065 - Rubber, Fabricated Parts.
- MIL-C-3702 - Cable, Power, Electrical, Ignition, High Tension.
- MIL-S-5059 - Steel, Corrosion Resistant (18-8), Plate, Sheet and Strip.
- MIL-I-24092 - Insulating Varnish, Electrical, Impregnating, Solvent Containing.

## STANDARDS

## FEDERAL

- FED-STD-313 - Material Safety Data Sheets Preparation and the Submission of.
- FED-STD-791 - Lubricant, Liquid Fuel and Related Products, Methods of Testing.

## MILITARY

- MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
- MIL-STD-290 - Packaging of Petroleum and Related Products.

(Copies of specifications, standards, handbooks, drawings, and publications required by manufacturers in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. The issues of the documents which are indicated as DoD adopted shall be the issue listed in the current DoDISS and the supplement thereto, if applicable.

## AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

- ASTM A 569 - Steel, Carbon (0.15 Maximum, Percent), Hot-Rolled Sheet and Strip, Commercial Quality.
- ASTM D 149 - Dielectric Breakdown, Voltage and Dielectric Strength of Electrical Insulating Materials at Commercial Power Frequencies.
- ASTM D 150 - A-C Loss Characteristics and Permittivity (Dielectric Constant) of Solid Electrical Insulating Materials.

## MIL-S-8660C

- ASTM D 217 - Cone Penetration of Lubricating Grease.  
 ASTM D 257 - D-C Resistance or Conductance of Insulating Materials.  
 ASTM D 495 - High Voltage, Low Current, Dry Arc Resistance of Solid Electrical Insulation.  
 ASTM D 1478 - Low-Temperature Torque of Ball Bearing Greases.

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

## SOCIETY OF AUTOMOTIVE ENGINEERS, INC (SAE)

- AMS 4377 - Sheet and Plate - 3.0 AL 1.0 Zn

(Application for copies should be addressed to SAE, 400 Commonwealth Drive, Warrendale, PA 15096.)

(Industry association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence.

## 3. REQUIREMENTS

3.1 Qualification. The silicone compound furnished under this specification shall be products which are qualified for listing on the applicable qualified products list at the time set for opening of bids (see 4.3 and 6.3).

3.2 Materials. The materials used in the formulation of the silicone compound shall be of high quality and suitable for the intended use. The final product shall be a smooth, non-lumpy grease-like compound.

3.2.1 Toxicity. The material shall have no adverse effect on the health of personnel when used for its intended purpose. Questions pertinent to this effect shall be referred by the contracting activity to the appropriate departmental medical service who will act as an adviser to the contracting agency.

3.2.2 Color. In its natural form, the compound shall be translucent and of a color similar to light gray or cream. When specified (see 6.2c), a dye or pigment may be incorporated in the material provided the finished compound meets the requirements of this specification in all other respects.

3.3 Performance characteristics.

3.3.1 Physical properties. Physical properties of the silicone compound shall be in accordance with the requirements in Table I.

3.3.2 Waterproof sealing. When tested as specified in 4.6.9, the test paper discs from 3 of the 5 tests shall show no pink coloration. Color changes within 1/8 inch of the edges of the test discs shall be disregarded.

## MIL-S-8660C

3.3.3 Electrical properties. Electrical properties of the silicone compound shall be in accordance with Table II.

3.3.4 Storage stability. Unworked and worked penetration of the compound after the 6 months of storage at  $37.8 \pm 3^{\circ}\text{C}$  ( $100 \pm 5^{\circ}\text{F}$ ) as specified in 4.6.14 taken at  $25 \pm 1^{\circ}\text{C}$  ( $77 \pm 2^{\circ}\text{F}$ ) shall conform to the requirement in Table I.

3.3.5 Workmanship. The compound shall be processed to produce a homogeneous mixture free from lumps, cakes, abrasives, and foreign materials.

## 4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Classification of inspection. The inspection requirements specified herein are classified as follows:

- a. Qualification inspection (see 4.3).
- b. Quality conformance inspection (see 4.4).

4.3 Qualification inspection. The qualification inspection shall consist of all the requirements and tests specified in Tables I and II.

4.3.1 Qualification inspection sample. The qualification inspection sample shall consist of 10 pounds of the compound packaged as specified in Section 5 of this specification. The sample shall be forwarded to the qualifying laboratory, Commander, Naval Air Development Center, Attention: Aircraft and Crew Systems Technical Directorate (6062), Warminster, PA 18974. The sample shall be plainly and durably marked with the following information:

Sample for qualification inspection  
 SILICONE COMPOUND, NATO CODE NUMBER S-736  
 MIL-S-8660C  
 Name of manufacturer  
 Product code number  
 Date of manufacture  
 Submitted by (name) (date) for qualification inspection in accordance with the requirements of MIL-S-8660C under authorization (reference authorizing letter) (see 6.3).

4.3.2 Manufacturer's data. Two copies of the manufacturer's test report, containing complete test data showing that material submitted for qualification conforms to the requirements of this specification, shall be submitted with the qualification sample. The location and identity of the plant which produced the sample tested shall also be supplied. Material safety data sheets on toxicity (see 3.2.1) shall be prepared in accordance with FED-STD-313 and submitted to the qualifying laboratory (see 4.3.1).

## MIL-S-8660C

4.3.3 Retention of qualification. In order to retain qualification of a product approved for listing on the qualified products list (QPL), the manufacturer shall verify by certification to the qualifying activity, that the manufacturer's product complies with the requirements of this specification. The time of periodic verification by certification shall be in two-year intervals from the date of original qualification. The Government reserves the right to re-examine the qualified product whenever deemed necessary to determine that the product continues to meet any or all of the specification requirements.

4.4 Quality conformance inspection.

4.4.1 Lot information. Unless otherwise specified herein or in the contract, a lot shall consist of all the silicone compound manufactured as one batch (see 6.4), forming part of one contract or order and submitted for inspection at one time.

4.4.2 Sampling for quality conformance inspection.

4.4.2.1 Sampling for tests. Two-5 pound samples of silicone compound shall be randomly selected from each lot and tested as specified in 4.4.3.1.

4.4.2.2 Sampling for packaging.

4.4.2.2.1 Unit container. A random sample of filled containers shall be selected from each lot in accordance with Inspection Level I of MIL-STD-105 and examined as specified in 4.4.3.2. The lot size shall be the total number of unit containers.

4.4.2.2.2 Shipping containers. Shipping containers, just prior to closure, shall be randomly selected from each lot in accordance with Inspection Level I of MIL-STD-105 and examined as specified in 4.4.3.2. The lot size shall be the total number of shipping containers.

4.4.3 Testing and examination of quality conformance samples.

4.4.3.1 Testing. The sample selected in 4.4.2.1 shall be tested to the requirements in Table III on a lot by lot basis or once in ten lots as specified in that table. Nonconformance of a test specimen to a single requirement in Table III shall be cause to reject the lot represented by the sample. Should the failure occur in a one in ten lot examination, the Government may, at its option, require testing on each subsequent lot.

4.4.3.2 Packaging. Samples selected in 4.4.2.2.1 and 4.4.2.2.2 shall be examined to the requirements in MIL-STD-290 and Table IV. The acceptable quality level (AQL) for this examination shall be 4.0 percent defective.

4.5 Test conditions.

4.5.1 Standard conditions. Standard laboratory conditions shall be  $25^{\circ}\text{C} \pm 1^{\circ}\text{C}$  ( $77^{\circ} \pm 2^{\circ}\text{F}$ ) with a relative humidity (RH) of  $50 \pm 5$  percent. Unless otherwise specified in the test method, testing of the silicone compound shall be at standard conditions.

## MIL-S-8660C

4.5.2 Specimen preparation. Unless otherwise specified, the compound shall be examined and tested as taken from the container without treatment or preconditioning of any kind. However, if the compound contains air bubbles, they shall be removed before testing by subjecting the compound to vacuum and heat.

4.6 Test methods.

4.6.1 Appearance. The silicone compound shall be visually examined for conformance to 3.2 and 3.2.2.

4.6.2 Insolubility. A determination of the compounds insolubility in solvents shall be made using distilled water, isopropyl alcohol (TT-I-735), ethyl alcohol (MIL-E-463), ethylene glycol (O-A-548) and glycerine (O-G-491).

4.6.2.1 Procedure. Approximately 3 grams of the compound, accurately weighed, shall be smeared around the inside of a weighed glass beaker, 250 ml capacity. Prepare 16 specimens in this manner. Three for each solvent (4.6.2) and one to act as control during the drying operation. Approximately 100 ml of the solvent, or enough to immerse the compound, shall be poured into the container. The container shall be tightly capped with metal foil and left to stand for a period of 7 days at standard conditions. At intervals of approximately 24 hours, the solution shall be stirred by moderate manual rotation of the container. At the end of the 7 day period, the solvent shall be poured off, and the container and compound rinsed carefully with successive washes of distilled water until all solvent has been removed. The container and compound shall be dried for 20 hours in an oven at  $70^{\circ} + 1^{\circ}\text{C}$  ( $160^{\circ} + 2^{\circ}\text{F}$ ) followed by drying over calcium chloride in a suitable desiccator. The degree of solubility in each solvent shall not exceed the requirement in Table I.

4.6.3 Penetration. Penetration of the compound, worked and unworked, shall be determined in accordance with ASTM D 217, except that the worked and unworked temperatures shall be those specified in Table I. Two specimens shall be tested for each temperature condition.

4.6.4 Flammability. A 10 gram specimen of the sample shall be placed on a 10 to 20 mesh stainless steel screen. The areas covered by the specimen shall be approximately 1 inch in diameter. The underside of the screen shall be cautiously heated with a Bunsen burner in a manner that will not cause the flame to project through or above the screen. As soon as the compound begins to decompose or volatilize, a second burner shall be used to ignite the vapors evolved. The material will be considered non-flammable if the burning ceases as both burners are withdrawn from the screen. Heating shall be continued until the sample is at a red heat; and both upper and under surfaces shall be examined for a self supporting flame. Two specimens shall be tested.

4.6.5 Corrosive effect. Corrosive effect of the silicone compound against various metals, combinations of metals, and non-metals shall be determined as specified in 4.6.5.1 through 4.6.5.2.

4.6.5.1 Specimen preparation.

4.6.5.1.1 Metals. All metal strips in Table V, except cadmium plated steel, shall be polished to a bright finish, swabbed with a hot suitable chemically pure solvent, followed by two successive 5 minute immersions in the

## MIL-S-8660C

same hot solvent. Each dry, polished strip shall be coated with the silicone compound. Combination of metals to be mated are identified in footnote 1/ of Table V. The mated metals and remaining individual metal strips shall be exposed as specified in 4.6.5.2. The number of strips in Table V will yield two test specimens for each kind of metal.

**4.6.5.1.2 Non-metals.** All non-metal materials shall be wiped with a dry clean, lintless cloth. Three specimens for each material identified in Table V are required. The silicone compound shall be coated on two specimens of each material, with the third piece acting as a control. All specimens shall be exposed as specified in 4.6.5.2.

**4.6.5.2 Procedure.** All specimens shall be placed in a convection current air oven maintained at  $100^{\circ}\text{C} \pm 1^{\circ}\text{C}$  ( $212^{\circ} \pm 2^{\circ}\text{F}$ ) for a period of 70(+1, -0) hours. Upon completion of the exposure period, all specimens shall be removed from the oven, wiped gently with a soft dry cloth to remove the compound (all mated strips shall be disassembled). Each specimen shall be visually examined for evidence of corrosion or degradation as specified in Table I. Change in hardness of the rubber specimens (compared to control) shall be determined using a Shore A durometer. The remaining non-metal specimens shall be given a scratch test, using a metal spatula, to determine apparent hardness changes.

**4.6.6 Volume change.** The percent change in volume of a rubber specimen due to swelling effect of the silicone compound shall be determined in accordance with Method 3603 of FED-STD-791, using the standard rubber NBR-L (see 6.6 and Table I) within 6 months of date of manufacture.

**4.6.7 High temperature weight loss (evaporation and bleeding).** The compound shall be tested in accordance with Method 321 of FED-STD-791, except as follows:

- a. Cone shall be suspended from a rod supported on the edges of the beaker without covering the beaker.
- b. Oven temperature shall be  $204^{\circ} \pm 6^{\circ}\text{C}$  ( $400^{\circ} \pm 10^{\circ}\text{F}$ ).
- c. Time shall be 30(+1, -0) hours.

**4.6.7.1 Evaporation.** The loss in weight of the entire assembly, after 30 hours at the test temperature, divided by the weight of the sample used, multiplied by 100 shall be reported as the percent evaporation.

**4.6.7.2 Bleeding.** The gain in weight of the beaker divided by the weight of the sample used, multiplied by 100 shall be reported as the percent bleeding.

**4.6.8 Low temperature torque.** Torque properties shall be determined in accordance with ASTM D 1478 at  $-54^{\circ} \pm 1^{\circ}\text{C}$  ( $-65^{\circ} \pm 2^{\circ}\text{F}$ ) with a 60 minute running time.

**4.6.9 Waterproof seal.** Five 7/8 inch disks of filter paper shall be dipped in a 25 percent by weight aqueous solution of cobaltous chloride, blotted off to remove excess solution and then dried at  $105^{\circ} \pm 1^{\circ}\text{C}$  ( $221^{\circ} \pm 2^{\circ}\text{F}$ ) until completely blue. The test paper disks shall then be placed in five Norma-Hoffman bomb oxidation dishes and the dishes filled with compound to be

## MIL-S-8660C

tested, avoiding incorporation of air bubbles. After leveling off the compound to the height of each dish, the latter shall be immersed in water at  $25^{\circ} \pm 3^{\circ}\text{C}$  ( $77^{\circ} \pm 5^{\circ}\text{F}$ ) for 24 hours, at the end of which time, the test paper disks shall be examined for development of a pink color.

**4.6.10 Dielectric strength.** Dielectric strength shall be determined in air at  $23^{\circ} \pm 2^{\circ}\text{C}$  ( $73.4^{\circ} \pm 3.6^{\circ}\text{F}$ ) and 50 + 5 percent RH and in accordance with ASTM D 149, except that 1/2 inch hemispherical electrodes shall be rigidly mounted with the axis in a horizontal plane, in a suitable apparatus. The electrodes shall be pressed into the compound in order to form the specified electrode gap. For lot inspection testing, an electrode gap of 0.050 inch shall be used.

**4.6.11 Volume resistivity.** Volume resistivity shall be determined in accordance with ASTM D 257, at  $23^{\circ} \pm 2^{\circ}\text{C}$  ( $73.4^{\circ} \pm 3.6^{\circ}\text{F}$ ) and RH of 50 + 5 percent. Test electrodes shall be in accordance with Figure 1. Extreme care should be exercised to avoid trapping air bubbles in the compound.

**4.6.12 Dielectric constant and dissipation factor.** Dielectric constant and dissipation factor shall be determined in accordance with ASTM D 150 with the compound spread in a layer 1/8 inch thick on the fixed electrode plate of the apparatus shown in Figure 1, using extreme care to avoid trapping air bubbles in the compound. The compound shall then be exposed to a temperature of  $23^{\circ}\text{C} \pm 2^{\circ}\text{C}$  ( $73.4^{\circ} \pm 3.6^{\circ}\text{F}$ ) and a RH of 50 + 5 percent for 24 hours. At the end of this period, the compound shall be tested at frequencies of 1 kilohertz (KHz), 1 megahertz (MHz), and 10 MHz for measurements of dissipation factor and dielectric constant. This test shall be performed in a suitable apparatus where the ratio of surface to thickness of compound layer is sufficient to give a capacitance of not less than 70 microfarads.

**4.6.13 Arc resistance.** The arc resistance time shall be determined in air at  $23^{\circ}\text{C} \pm 2^{\circ}\text{C}$  ( $73.4^{\circ} \pm 3.6^{\circ}\text{F}$ ) and a RH of 50 + 5 percent RH in accordance with ASTM D 495, except that the test shall be conducted using a 1/8 inch layer of the compound spread on a layer of thermal glass, such as quartz, Pyrex, etc. The electrodes shall consist of two tungsten rods 0.186 inch diameter, with tips 0.060 inch in diameter, which have conical points with a 60 degree included angle. The electrodes shall be mounted to an insulated block at 45 degrees to the vertical, and shall be adjusted to give a gap of 0.320 inch. Both electrodes shall be in the same horizontal and vertical planes. The arc electrodes shall be cleaned with a soft clean cloth dampened with alcohol, then dried with a soft, clean dry cloth before each determination. The time in seconds from the start of test until failure of the material shall be recorded as the measure of the arc resistance of the compound. Failure shall be considered to have occurred at the instant that a continuous bright line is completed between the electrodes.

**4.6.14 Storage stability.** The penetration after storage shall be determined on an unworked and a worked sample of compound which has been stored at a temperature of  $37.8^{\circ} \pm 3^{\circ}\text{C}$  ( $100^{\circ} \pm 5^{\circ}\text{F}$ ) in a 1 pound oiltight container for 6 months subsequent to the original determination of the unworked and worked penetration. The unworked and worked penetration, after storage, shall be determined as specified in 4.6.3.



## MIL-S-8660C

## 5. PACKAGING

5.1 Preservation, packing and marking. The silicone compound shall be preserved, packed and marked in accordance with the provisions of MIL-STD-290 and in accordance with the details specified by the acquiring activity with respect to the various options, choices, and alternatives indicated in MIL-STD-290 (see 6.2.1e and f).

## 6. NOTES

6.1 Intended use. The compound covered by this specification is intended for use, as follows:

- a. As a lubricant and sealant for rubber components, such as "O" rings and gaskets.
- b. When mixed with molybdenum disulfide powder, as a lubricant for threaded connections on piping and valves to be used with liquids and gases.
- c. As a sealant to prevent galvanic corrosion due to moisture penetration in areas of dissimilar metal contact.
- d. For use under extreme conditions of service and storage, where freezing at  $-54^{\circ}\text{C}$ . ( $-65^{\circ}\text{F}$ ) or exudation and deterioration at  $+204^{\circ}\text{C}$  ( $+400^{\circ}\text{F}$ ) is not permissible, and wherein water insolubility and sealing properties are essential.
- e. For sealing high tension electrical connections of aircraft and automotive engines.
- f. For sealing and insulating electronic equipment, subassemblies and components where it is essential that the material remain in a soft state in order to allow easy disassembly or change.
- g. As a sealant to protect the threads on shells from moisture and corrosion. When used in this manner, the silicone compound should not come into contact with surfaces that are to be painted.

6.1.1 Use restrictions. This silicone compound is not intended for use as a heat sink. Materials having more suitable properties are available commercially.

6.2 Ordering data. Acquisition documents should specify the following:

- a. Title, number and date of this specification.
- b. Quantity desired in pounds.
- c. Color of dye or pigment, if required (see 3.2.2).

## MIL-S-8660C

- d. Size and type of container in which silicone compound is to be furnished.
- e. Levels of preservation and packing (see 5.1).
- f. Other options, choices and alternatives of MIL-STD-290 (see 5.1).

**6.3 Qualification.** With respect to products requiring qualification, awards will be made only for products which are, at the time set for opening of bids, qualified for inclusion in qualified products list (QPL 8660) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or purchase orders for the products covered by this specification. The activity responsible for the Qualified Products List is the Naval Air Systems Command, Washington, DC 20361; however, information pertaining to qualification of products and letter of authorization for submittal of sample may be obtained from the Commander, Naval Air Development Center, Attn: Aircraft and Crew Systems Technical Directorate (Code 6062), Warminster, PA 18974.

**6.4 Batch.** A batch is defined as the end product of all raw materials mixed or blended in a single operation.

**6.5 International standardization agreements.** Certain provisions of this specification (see 1.1) are the subject of international standardization agreement, ASCC AIR STD 15/1, ABC-NAVY STD 17, and NATO STANAG NAT-STD-1135. When amendment, revision, or cancellation of this specification is proposed, which will affect or violate the international agreement concerned, the preparing activity should take appropriate reconciliation action through international standardization channels including departmental standardization offices, if required.

**6.6 Standard rubber samples.** Samples of the standard synthetic rubber NBR-L for the test specified in 4.6.6 may be obtained from the Precision Rubber Products Corp. Aerospace Division, 1217 South 26 Place, Phoenix, AZ 85035.

**6.7 Changes from previous issue.** Asterisks are not used in this specification to identify changes with respect to the previous issue, due to the extensiveness of the changes.

**Custodians:**

Army - MR  
Navy - AS  
Air Force - 20

**Preparing activity:**

Navy - AS

(Project 6850-0713)

**Review activities:**

Army - ER, GL, MI  
Navy - OS, YD  
DLA - GS

**User activities:**

Army - ME

## MIL-S-8660C

TABLE I. Physical properties.

Characteristic	Paragraph	
	Requirement	Test
Insolubility, percent weight loss, maximum, in:		4.6.2
Distilled water	0.4	
Isopropyl alcohol	10.0	
Ethyl alcohol	7.0	
Ethylene glycol	0.5	
Glycerine	0.5	
Penetration at standard conditions:		4.6.3
Unworked	230 + 30	
Worked, maximum	3T0	
Worked, after 24 hours at $204 \pm 5^{\circ}\text{C}$ ( $400^{\circ} \pm 10^{\circ}\text{F}$ )	310	
Flammability	Nonflammable	4.6.4
Corrosive effect:		4.6.5
On metals	No pitting or other visual evidence of corrosion.	
On non-metals	No change in appearance when compared to control. No change in hardness.	
Volume change of rubber, percent maximum, after 168 hours at $70^{\circ} \pm 1^{\circ}\text{C}$ ( $158^{\circ} \pm 2^{\circ}\text{F}$ )	7	4.6.6
High temperature, percent weight loss, maximum:		4.6.7
Evaporation	2	
Bleeding	8	
Low temperature torque, gram-cm, maximum:		4.6.8
Starting	5,000	
Running	1,000	

## MIL-S-8660C

TABLE II. Electrical properties.

Characteristic	Paragraph	
	Requirement	Test
Dielectric strength, volts/mil, minimum 0.050 inch electrode gap 0.010 inch electrode gap	300 500	4.6.10
Volume resistivity, OHM-cm minimum at 23° + 1.1°C (73.4° + 2°F) 177° + 1.1°C (350° ± 2°F)	1.0 x 10 <sup>13</sup> 1.0 x 10 <sup>12</sup>	4.6.11
Dielectric constant, maximum: 1 Kiloherztz 1 Megahertz 10 Megahertz	3.1 3.1 3.1	4.6.12
Dissipation factor, maximum; 1 Kiloherztz 1 Megahertz 10 Megahertz	0.0025 0.0025 0.0025	4.6.12
Arc resistance, seconds, minimum	60	4.6.13

## MIL-S-8660C

TABLE III. Quality conformance - physical tests.

Characteristic	Paragraph	
	Requirement	Test
<u>Testing each lot:</u>		
Penetration	Table I	4.6.3
High temperature weight loss	Table I	4.6.7
Waterproof seal	3.3.2	4.6.9
<u>Testing every tenth lot:</u>		
Flammability	Table I	4.6.4
Corrosive effect	Table I	4.6.5
Low temperature torque	Table I	4.6.8
Dielectric strength	Table II	4.6.10
Dielectric constant and dissipation factor	Table II	4.6.12
Arc resistance	Table II	4.6.13

TABLE IV. Quality conformance packaging inspection

	Defect
Packaging	Unit containers not as specified.
Packing	Packing materials not as specified. Not in accordance with contract requirements.  Container not as specified, closure not accomplished by specified or required methods or materials.  Inadequate application of components, such as incomplete closures of case liners, container flaps, loose or inadequate strappings, bulged or distorted containers.
Count	Less than specified or indicated quantity.
Weight	Individual weight of container less than indicated or specified.
Markings	Interior or exterior markings (as applicable) omitted, illegible, incorrect, incomplete, or not in accordance with contract requirements.

## MIL-S-8660C

TABLE V. Test specimens for corrosive effects


Material	Specification	Required Number <u>1/</u>	Size 2/ (inch)
<b><u>METALS:</u></b>			
Aluminum alloy	QQ-A-250/4	6	-
Copper	QQ-C-502	4	-
Lead	QQ-L-201	2	-
Magnesium alloy	AMS 4377	4	-
Solder	QQ-S-571	2	-
Steel	ASTM A 569	4	-
Zinc	QQ-Z-301	4	-
Cadmium plated steel	QQ-P-416	2	-
Brass	QQ-B-613	2	-
Stainless steel	MIL-S-5059	2	-
<b><u>NON-METALS:</u></b>			
Chloroprene ignition cable	MIL-C-3702, Grade C	3	6 length
Silicone ignition cable	MIL-C-3702, Grade B	3	6 length
Rubber	MIL-R-3065, Class RN	3	2 by 2 by 0.5
Rubber	MIL-R-3065, Class RS	3	2 by 2 by 0.5
Varnish	MIL-I-24092	3	<u>3/</u>
Enamel	MIL-E-480	3	<u>3/</u>
PVC	MIL-I-631, Type F, Grade B	3	-
Molding plastic	MIL-M-14, CMG	3	-
Molding plastic	MIL-M-14, MFE	3	-

1/ After coating all metal specimens, mate the following: 2 aluminum alloy to 2 copper; 2 aluminum alloy to 2 cadmium plates; 2 magnesium alloy to steel; and 2 brass to 2 stainless steel strips. All other strips shall be exposed individually.

2/ Sizes, when not specified, shall be of a suitable size to permit evaluation after the exposure period.

3/ In order to evaluate the varnish and enamel, coat any suitable panel with the liquid, allow to dry, then overcoat with the silicone compound.

MIL-S-8660C

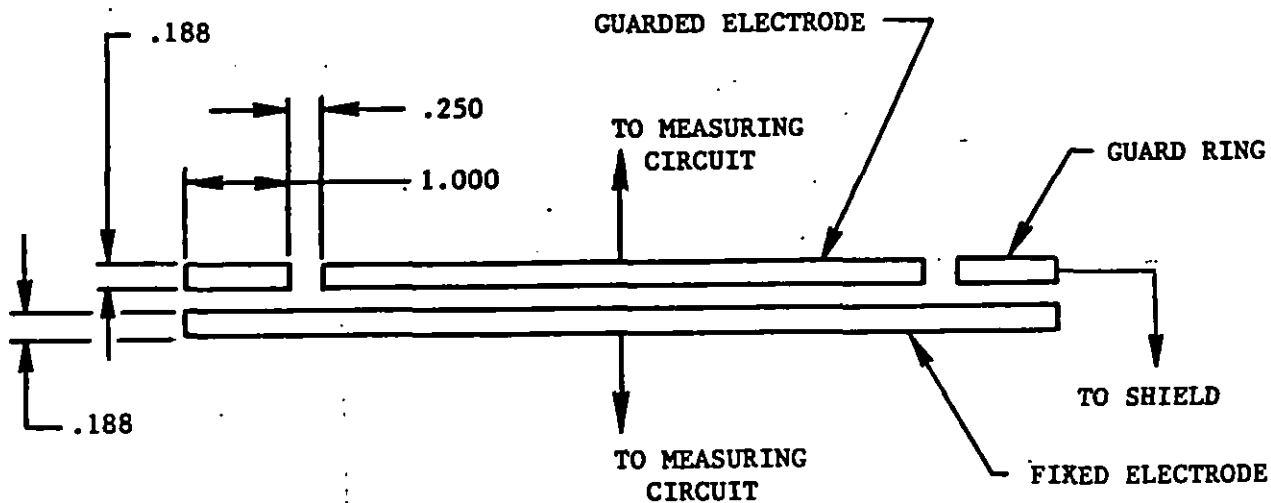

ELECTRODES SHALL BE OF POLISHED BRASS.

FOR TESTS AT FREQUENCIES OF 1 KHz AND 1 MHz PER SECOND, THE GUARDED ELECTRODE SHALL BE A DISK 6 INCHES IN DIAMETER. THE THICKNESS OF THE SPECIMEN SHALL BE 0.125 INCH.

FOR TESTS MADE AT A FREQUENCY OF 10 MHz PER SECOND, THE GUARDED ELECTRODE SHALL BE A DISK 2 INCHES IN DIAMETER. THE THICKNESS OF THE TEST SPECIMEN SHALL BE SUCH AS TO GIVE A CAPACITANCE OF BETWEEN 15 UUF and 45 UUF.

DIMENSION IN INCHES.

FIGURE 1. Test electrodes for electrical resistance (volume), and dielectric constant and dissipation factor tests.

**INSTRUCTIONS:** In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge (*DO NOT STAPLE*), and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

**NOTE:** This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE NAVY  
Commanding Officer  
Naval Air Engineering Center  
Engineering Specifications and Standards Department  
(ESSD), Code 93  
Lakehurst, NJ 08733




NO POSTAGE  
NECESSARY  
IF MAILED  
IN THE  
UNITED STATES

OFFICIAL BUSINESS  
PENALTY FOR PRIVATE USE \$300

**BUSINESS REPLY MAIL**  
FIRST CLASS PERMIT NO. 12503 WASHINGTON D C

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE NAVY

Commanding Officer  
Naval Air Engineering Center  
Engineering Specifications and Standards Dept.  
(ESSD), Code 93  
Lakehurst, NJ 08733

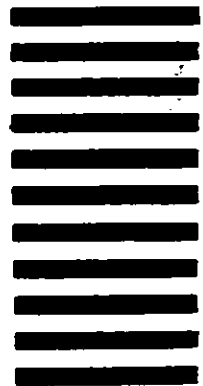



## STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

*(See Instructions - Reverse Side)*

**1. DOCUMENT NUMBER**  
MIL-S-8660C

**2. DOCUMENT TITLE**  
Silicone Compound, NATO Code Number S-763

**3a. NAME OF SUBMITTING ORGANIZATION**

**4. TYPE OF ORGANIZATION (Mark one)**

VENDOR

USER

MANUFACTURER

OTHER (Specify): \_\_\_\_\_

**b. ADDRESS (Street, City, State, ZIP Code)**

**5. PROBLEM AREAS**

**a. Paragraph Number and Wording:**

**b. Recommended Wording:**

**c. Reason/Rationale for Recommendation:**

**6. REMARKS**

**7a. NAME OF SUBMITTER (Last, First, MI) - Optional**

**b. WORK TELEPHONE NUMBER (Include Area Code) - Optional**

**c. MAILING ADDRESS (Street, City, State, ZIP Code) - Optional**

**8. DATE OF SUBMISSION (YYMMDD)**