

INCH-POUND

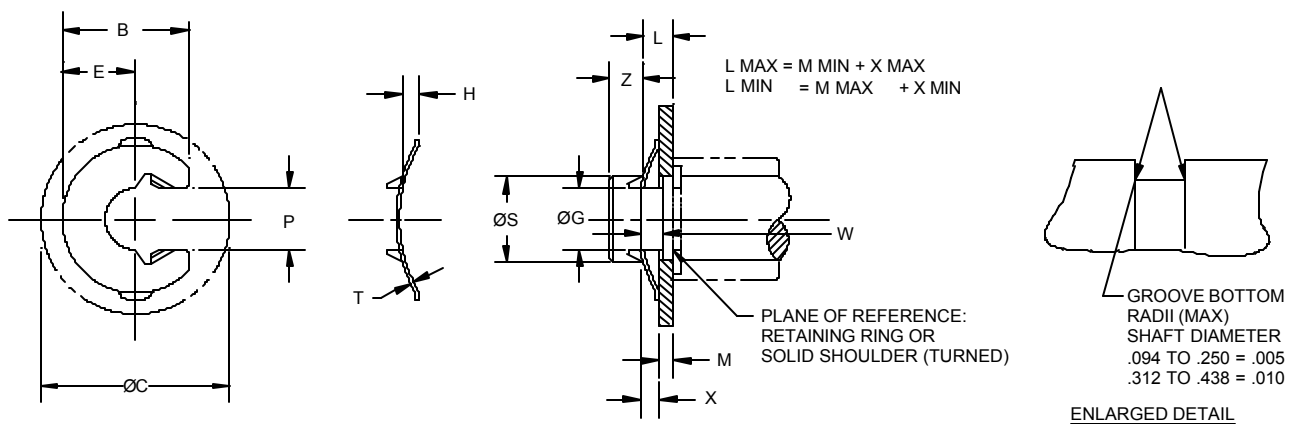
MS3216C
 23 FEBRUARY 2004
 SUPERSEDING
 MS3216B
 28 JUNE 1995

MS SPECIFICATION SHEET

RING, RETAINING, EXTERNAL, PRONG-LOCK
 (REDUCED SECTION TYPE)

This specification sheet is approved for use by all
 Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this MS specification sheet.

Table I. Dimensions.

| ØShaft (Ref) | | ØP Free Gap | | B Overall Height | | E | H Bow Height | T ^{1/} Thickness | | ØG | | W Width | ØC Clear- ance |
|-----------------|------|-------------------|--------|------------------------|--------|-------|--------------------|------------------------------|--------|-------|-----------------------------------|------------------|----------------------|
| Inch | mm | Basic | Tol | Basic | Tol | (Ref) | ±.010 | Basic | Tol | Basic | Tol | + .005 - .000 | Inch |
| .094 | 2.4 | .063 | ± .004 | .307 | ± .010 | .166 | .050 | .010 | ± .001 | .061 | ± .001 .003 FIM ^{2/} | .035 | .370 |
| .125 | 3.2 | .086 | | .307 | | .166 | .050 | .010 | | .082 | ± .0015 .003 FIM ^{2/} | .035 | .370 |
| .156 | 4.0 | .108 | ± .005 | .330 | | .184 | .055 | .010 | ± .002 | .104 | ± .002 .004 FIM ^{2/} | .040 | .410 |
| .188 | 4.8 | .130 | | .390 | | .213 | .060 | .015 | | .124 | ± .003 .005 FIM ^{2/} | .045 | .480 |
| .250 | 6.3 | .172 | | .500 | | .280 | .070 | .015 | | .165 | | .055 | .620 |
| .312 | 7.9 | .234 | ± .010 | .620 | ± .020 | .360 | .095 | .015 | | .228 | | .080 | .790 |
| .375 | 9.5 | .280 | | .740 | | .427 | .130 | .020 | | .270 | | .095 | .940 |
| .438 | 11.1 | .340 | | .820 | | .475 | .130 | .020 | | .327 | | .105 | 1.050 |

^{1/} T = Thickness "T" applies to unplated rings. For corrosion resistant steel and plated rings, +.002 should be added to the maximum tolerance, i.e., ±.002 should be +.004/-.002.

^{2/} FIM = (Full Indicator Movement) is the maximum allowable deviation of concentricity between the groove and the shaft.

MS3216C

Table I. Dimensions. (continued)

| Ø Shaft (Ref) | | X Distance from outer groove wall to face of retained part | | Resilient take-up of tolerances of L and M | Approx Average Resistance (lb) within X max and X min | | | | Approx force to flatten | |
|------------------|------|---|------|---|--|--------------------------|-----------------------------|--------------------------|-----------------------------|--------------------------|
| | | | | | Rings of | | | | Rings of | |
| | | | | | Carbon steel and CRES | Beryl- lium copper | Carbon steel and CRES | Beryl- lium copper | Carbon steel and CRES | Beryl- lium copper |
| Inch | mm | Min | Max | X max X min | As installed | | After plating | | lb | lb |
| .094 | 2.4 | .030 | .038 | .008 | 9 | 6.5 | 3.5 | 2.5 | 30 | 20 |
| .125 | 3.2 | .030 | .040 | .010 | 8 | 5 | 3 | 2.5 | 30 | 20 |
| .156 | 4.0 | .035 | .045 | .010 | 8 | 5 | 4 | 2.5 | 30 | 20 |
| .188 | 4.8 | .039 | .049 | .010 | 20 | 13 | 5.5 | 4.5 | 60 | 40 |
| .250 | 6.3 | .045 | .060 | .015 | 15 | 10.5 | 7 | 5 | 60 | 40 |
| .312 | 7.9 | .070 | .085 | .015 | 6 | 5 | 4 | 3.5 | 60 | 40 |
| .375 | 9.5 | .080 | .105 | .025 | 19 | 14 | 7 | 5.5 | 80 | 50 |
| .438 | 11.1 | .095 | .120 | .025 | 12 | 9 | 6 | 5 | 60 | 40 |

REQUIREMENTS:

1. **Classification:** Retaining rings furnished under this standard shall be Type II, Class 4 of the procurement specification.
2. **Material:**
 - (a) Carbon spring steel, grade 1060 thru 1095 (UNS G10600 thru G10950) in accordance with ASTM A682 as applicable or A568/A568M.
 - (b) Corrosion resistant steel in accordance with AMS 5520 (UNS S15700).
 - (c) Beryllium copper alloy number 170 (UNS C17000) or alloy number 172 (UNS C17200) in accordance with ASTM B194.
3. **Hardness:**

TABLE II. Hardness

| Ø Shaft (Ref) | Carbon Steel | Corrosion Resistant Steel | Beryllium Copper |
|---|----------------------------------|----------------------------------|---------------------|
| .094 to .250 incl .094 to .312 incl .094 to .438 incl .312 to .438 incl .375 and .438 | 83.5-86HR15N 65-69.5HR3ON | 82.5-86HR15N 63-69.5HR3ON | 77-82HR15N |

4. **Protective finish or surface treatment:**
 - (a) Carbon steel - shall be as specified (see table III):
 - (1) Cadmium plate in accordance with SAE-AMS-QQ-P-416, Type II, Class 3 or ASTM B696, Type II, Class 5 or zinc-nickel plate in accordance with AMS 2417, Type 2.
 - (2) Zinc coat in accordance with ASTM B633, type II, class Fe/Zn5, or ASTM B695, Type II, Class 5.
 - (3) Phosphate coat in accordance with MIL-DTL-16232, Type Z, Class 2.
 - (b) Corrosion resistant steel - shall be cleaned, descaled and passivated in accordance with SAE-AMS-QQ-P-35.

MS3216C

5. Procurement specification: MIL-R 21248.
6. Part number: The basic MS part number is followed by a dash number taken from table III.

Example: MS3216-1025 is the part number for a carbon steel cadmium plate, external, prong-lock, retaining ring for use on a .250 diameter shaft.
7. Unless otherwise specified, all dimensions are in inches.
8. In the event of a conflict between the text of this document and the references cited herein, the text of this document shall take precedence.
9. Unless otherwise specified, issues of referenced documents are those in effect at the time of solicitation.
10. Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

TABLE III. Dash numbers for MS3216

| ØS Shaft (Ref) | <u>1/</u> Carbon Steel Cadmium Plate or Zinc-Nickel | <u>1/</u> Carbon Steel Zinc-Coat | <u>1/</u> Carbon Steel Phosphate Coat | Steel Corrosion Resistant | <u>1/</u> Beryllium Copper |
|----------------------|--|--|---|------------------------------|----------------------------------|
| | Dash No. | Dash No. | Dash No. | Dash No. | Dash No. |
| .094 | -1009 | -2009 | -3009 | -4009 | -5009 |
| .125 | -1012 | -2012 | -3012 | -4012 | -5012 |
| .156 | -1015 | -2015 | -3015 | -4015 | -5015 |
| .188 | -1018 | -2018 | -3018 | -4018 | -5018 |
| .250 | -1025 | -2025 | -3025 | -4025 | -5025 |
| .312 | -1031 | -2031 | -3031 | -4031 | -5031 |
| .375 | -1037 | -2037 | -3037 | -4037 | -5037 |
| .438 | -1043 | -2043 | -3043 | -4043 | -5043 |

- 1/ Substitute corrosion resistant steel when used in food processing machinery, or in fuel or lubrication systems, or when used at temperatures over 450 °F (233 °C).

MS3216C

Recommended design limitations and usage.

- (a) Intended use - To provide large shoulders for positioning and maintaining machine parts. They are applied radially and are locked positively in their groove by means of two prongs extending from the inner circumference to the open end. They withstand high thrust loads and relative rotation between the retained parts. Their bowed construction provides resilient end-play take-up in axial direction. They may be assembled and disassembled with a screwdriver or with the prong-lock applicator. Sizes .125 to .312 are available rod-stacked for high speed application. The use of the following formulas are based on the fact that the ring material will not fail in compression. Limitation on use - the following formulas are not to be used for brittle materials such as cast iron, etc.

Warning - Rings shall not be over expanded during installation since this will lead to ring failure.

- (b) Allowable thrust load capacity of the rings. Abutting components to have sharp corners =

$$P = \frac{pSTX}{1.75F} \quad \text{where}$$

P = Allowable thrust load (pounds).
 S = Shaft diameter (inches).
 T = Ring thickness (inches).
 X = Ultimate shear strength of the ring material (psi). ^{1/}
 F = Factor of safety.

A safety factor, $F = 3$, is recommended, since the ring after flattening under load is subjected not only to pure shear stresses but also to bending stresses.

- (c) Allowable load capacity of groove wall =

$$P = \frac{pSdY}{2F} \quad \text{where}$$

P = Allowable compression load (pounds)
 S = Shaft diameter (inches)
 d = Groove depth (inches)
 Y = Yield strength in compression of the groove material (psi)
 F = Factor of safety

To insure a safe working load a safety factor, $F = 3$, is recommended, since the working stress in the groove section is raised considerably by the notch effect of the deep groove.

- (d) Minimum distance between outer groove wall and end of shaft =

$$Z = 2d \quad \text{where:}$$

Z = Minimum distance between outer groove wall and end of shaft (inches)
 d = Groove depth (inches)

- (e) Differential rotation =

Differential rotation of ring and adjacent part creates no element of risk, because the ring is locked in its groove by two locking prongs.

- ^{1/} $X = 130,000$ psi ultimate shear strength for rings of carbon steel or corrosion resistant steel.
 $X = 110,000$ psi ultimate shear strength for rings of beryllium copper.

MILITARY INTEREST

Custodians:

Army - AR

Navy - OS

Air Force - 99

Preparing activity:

DLA - IS

(Project 6325-1177)

Review Activities:

Army - AT, CR4, MI

Navy - MC