

AFML-TR-73-114

AD 762305

ENGINEERING DATA ON NEW AEROSPACE STRUCTURAL MATERIALS


O. L. Deel, P. E. Ruff and H. Mindlin

Battelle
Columbus Laboratories

TECHNICAL REPORT AFML-TR-73-114

JUNE 1973

Reproduced by
NATIONAL TECHNICAL
INFORMATION SERVICE
U.S. Department of Commerce
Springfield VA 22151

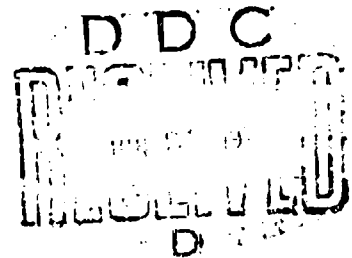

Approved for public release; distribution unlimited.

Air Force Materials Laboratory
Air Force Systems Command
Wright-Patterson Air Force Base, Ohio

NOTICE

When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

NTIS		✓
DDC		
UNCLASSIFIED		
DATE		
BY		
A		

Copies of this report should not be returned unless return is required by security considerations, contractual obligations, or notice on a specific document.

DOCUMENT CONTROL DATA - R & D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1. ORIGINAL NO. ACTIVITY (Corporate Author) Battelle Columbus Laboratories 505 King Avenue, Columbus, Ohio 43201		2a. REPORT SECURITY CLASSIFICATION Unclassified	
		2b. GROUP NA	
3. REPORT TITLE Engineering Data on New Aerospace Structural Materials			
4. DESCRIPTIVE NOTES (Type of report and inclusive dates) Final Summary Report, April 1972 to April 1973			
5. AUTHOR(S) (First name, middle initial, last name) Omar L. Deel, Paul E. Ruff, and H. Mindlin			
6. REPORT DATE June 1973		7a. TOTAL NO. OF PAGES	7b. NO. OF REFS 0
8a. CONTRACT OR GRANT NO. F33615-72-C-1280		8b. ORIGINATOR'S REPORT NUMBER(S) AFML-TR-73-114	
8c. PROJECT NO. 7381		9. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
8d. Task No. 738106			
10. DISTRIBUTION STATEMENT Approved for public release; distribution unlimited.			
11. SUPPLEMENTARY NOTES		12. SPONSORING MILITARY ACTIVITY Air Force Materials Laboratory Wright-Patterson Air Force Base, Ohio 45433	
13. ABSTRACT The major objectives of this research program were to evaluate newly developed materials of interest to the Air Force for potential structural airframe usage, and to provide "data sheet" type presentations of engineering data for these materials. The effort covered in this report has concentrated on X2048-T851 plate, 7050-T73651 plate, 21-6-9 annealed sheet, Ti-8Mo-8V-2Fe-3Al STA sheet, Ti-6Al-2Zr-2Sn-2Mo-2Cr STA plate, and Ti-6Al-6V-2Sn STA isothermal die forgings. The properties investigated include tension, compression, shear, bend, impact, fracture toughness, fatigue, creep and stress-rupture, and stress corrosion at selected temperatures.			


DD FORM 1473
1 NOV 65

Security Classification

14 KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Mechanical Properties						
Fatigue Properties						
Creep Properties						
Chemical Composition						
Physical Properties						
Aluminum Alloys						
Stainless Steel						
Titanium Alloys						
X-2048						
21-6-9						
7050						
Ti-8Mo-8V-2Fe-3Al						
Ti-6Al-2Zr-2Sn-2Mo-2Cr						
Ti-6Al-6V-2Sn						
<i>ja</i>						

ENGINEERING DATA ON NEW
AEROSPACE STRUCTURAL MATERIALS

O. L. Deel, P. E. Ruff and H. Mindlin

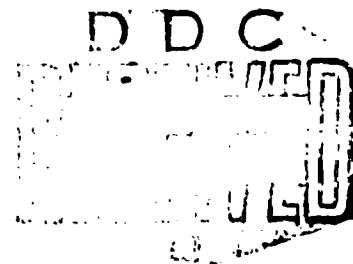

Approved for public release; distribution unlimited.

ib

FOREWORD

This report was prepared by Battelle's Columbus Laboratories, Columbus, Ohio, under Contract F33615-72-C-1280. This contract was performed under Project No. 7381, "Materials Applications", Task No. 738106, "Engineering and Design Data". The work was administered under the direction of the Air Force Materials Laboratory, Air Force Systems Command, Wright-Patterson Air Force Base, Ohio, by Mr. Clayton Harmsworth (AFML/MXE), technical manager.

This final report covers work conducted from April, 1972, to April, 1973. This report was submitted by the authors on April 30, 1973.

This technical report has been reviewed and is approved.

A. Olevitch

A. Olevitch
Chief, Materials Engineering Branch
Materials Support Division
Air Force Materials Laboratory

ABSTRACT

The major objectives of this research program were to evaluate newly developed materials of interest to the Air Force for potential structural air-frame usage, and to provide "data sheet" type presentations of engineering data for these materials. The effort covered in this report has concentrated on X2048-T851 plate, 7050-T73651 plate, 21-6-9 annealed sheet, Ti-8Mo-8V-2Fe-3Al STA sheet, Ti-6Al-2Zr-2Sn-2Mo-2Cr STA plate, and Ti-6Al-6V-2Sn STA isothermal die forgings.

The properties investigated include tension, compression, shear, bend, impact, fracture toughness, fatigue, creep and stress-rupture, and stress corrosion at selected temperatures.

	<u>Page</u>
INTRODUCTION	1
X2048-T351 Aluminum Alloy	2
Material Description	2
Processing and Heat Treating	2
Test Results	2
7050-T73651 Aluminum Alloy	19
Material Description	19
Processing and Heat Treating	19
Test Results	19
21-6-9 Stainless Steel Alloy	36
Material Description	36
Processing and Heat Treating	36
Test Results	36
Ti-8Mo-8V-2Fe-3Al Alloy	52
Material Description	52
Processing and Heat Treating	52
Test Results	52
Ti-6Al-2Zr-2Sn-2Mo-2Cr Alloy	68
Material Description	68
Processing and Heat Treating	68
Test Results	68
Ti-6Al-6V-2Sn Isothermal Die Forgings	85
Material Description	85
Processing and Heat Treating	85
Test Results	85
DISCUSSION OF PROGRAM RESULTS	98
CONCLUSIONS	98

APPENDIX I

EXPERIMENTAL PROCEDURE	101
Mechanical Properties	102
Specimen Identification	103
Test Description	104
Tension	104
Compression	105
Shear	105
Bend	105
Creep and Stress Rupture	105

Preceding page blank

TABLE OF CONTENTS
(Continued)

	<u>Page</u>
APPENDIX I (Continued)	
Stress Corrosion	106
Thermal Expansion	107
Fatigue	107
Fracture Toughness	108
APPENDIX II	
SPECIMEN DRAWINGS	109
APPENDIX III	
DATA SHEETS	113

LIST OF TABLES

		<u>Page</u>
Table I	Tension Test Results for X2048-T851 Aluminum Plate	5
II	Compression Test Results for X2048-T851 Aluminum Plate	6
III	Shear Test Results for X2048-T851 Aluminum Plate at Room Temperature	7
IV	Charpy V-Notch Test Results for X2048-T851 Aluminum Plate.	7
V	Results of Slow-Bend Type Fracture Toughness Tests for X2048-T851 Aluminum Plate	8
VI	Axial Load Fatigue Test Results for X2048-T851 Aluminum Plate (Unnotched, $R = 0.1$) (Longitudinal)	9
VII	Axial Load Fatigue Results for X2048-T851 Aluminum Plate (Notched, $K_t = 3.0$, $R = 0.1$) (Longitudinal)	10
VIII	Summary Data on Creep and Rupture Properties for X2048- T851 Aluminum Plate (Longitudinal)	11
IX	Tension Test Results for 7050-T73651 Aluminum Alloy Plate.	22
X	Compression Test Results for 7050-T73651 Aluminum Alloy Plate	23
XI	Shear Test Results for 7050-T73651 Aluminum Alloy Plate at Room Temperature	24
XII	Impact Test Results for 7050-T73651 Aluminum Alloy Plate at Room Temperature	24
XIII	Results of Slow-Bend Type Fracture Toughness Tests for 7050-T73651 Aluminum Alloy Plate	25
XIV	Axial Load Fatigue Test Results for Unnotched 7050-T73651 Aluminum Plate (Transverse)	26
XV	Axial Load Fatigue Test Results for Notched ($K_t = 3.0$) 7050-T73651 Aluminum Plate (Transverse)	27
XVI	Summary Data on Creep and Rupture Properties for 7050 Aluminum Plate (Transverse)	28
XVII	Tensile Test Results for Annealed 21-6-9 Stainless Steel Sheet	39
XVIII	Compression Test Results for Annealed 21-6-9 Stainless Steel Sheet	40

LIST OF TABLES
(Continued)

		<u>Page</u>
Table XIX	Shear Test Results for Annealed 21-6-9 Stainless Steel Sheet at Room Temperature	41
XX	Axial Load Fatigue Test Results for Unnotched 21-6-9 Annealed Stainless Steel Sheet (Transverse)	42
XXI	Axial Load Fatigue Test Results for Notched ($K_t = 3.0$) 21-6-9 Annealed Stainless Steel Sheet (Transverse)	43
XXII	Summary Data on Creep and Rupture Properties for 21-6-9 Stainless Steel Sheet (Transverse)	44
XXIII	Tensile Test Results for Solution-Treated and Aged Ti-8Mo-8V-2Fe-3Al Alloy Sheet	55
XXIV	Compression Test Results for Solution-Treated and Aged Ti-8Mo-8V-2Fe-3Al Alloy Sheet	56
XXV	Shear Test Results for Solution-Treated and Aged Ti-8Mo-8V-2Fe-3Al Alloy Sheet at Room Temperature	57
XXVI	Axial Load Fatigue Test Results for Unnotched, Solution-Treated and Aged Ti-8Mo-8V-2Fe-3Al Alloy Sheet (Transverse)	58
XXVII	Axial Load Fatigue Test Results for Notched ($K_t = 3.0$) Solution-Treated and Aged Ti-8Mo-8V-2Fe-3Al Alloy Sheet (Transverse)	59
XXVIII	Summary Data on Creep and Rupture Properties for Ti-8Mo-8V-2Fe-3Al Alloy Sheet (Transverse)	60
XXIX	Tensile Test Results for Solution-Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Alloy Plate	71
XXX	Compression Test Results for Solution-Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Alloy Plate	72
XXXI	Shear Test Results for Solution-Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Alloy Plate at Room Temperature	73
XXXII	Impact Test Results for Solution-Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Alloy Plate at Room Temperature	73
XXXIII	Results of Slow-Bend Type Fracture Toughness Tests on Solution-Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Plate	74
XXXIV	Axial Load Fatigue Test Results for Unnotched Solution-Treated and Aged Ti-6Al-2Sn-2Mo-2Cr Alloy Plate (Transverse)	75

LIST OF TABLES
(Continued)

		<u>Page</u>
Table XXXV	Axial Load Fatigue Test Results for Notched ($K_t = 3.0$) Solution-Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Alloy Plate (Transverse)	76
XXXVI	Summary Data on Creep and Rupture Properties for Solution- Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Alloy Plate (Transverse)	7
XXXVII	Tension Test Results for Solution-Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forging (Transverse)	87
XXXVIII	Compression Test Results for Solution-Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings (Transverse)	88
XXXIX	Shear Test Results at Room Temperature for Solution- Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings	89
XL	Impact Test Results for Solution-Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings	89
XLI	Axial Load Fatigue Test Results for Unnotched Solution- Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings	90
XLII	Axial Load Fatigue Test Results for Notched ($K_t = 3.0$) Solution-Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings	91
XLIII	Summary Data on Creep and Rupture Properties for Solution- Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings (Transverse)	92

LIST OF ILLUSTRATIONS

	<u>Page</u>
Figure 1. Specimens Layout for X2048-T851 Plate	3
2 Typical Tensile Stress-Strain Curves at Temperature for X2048-T851 Plate (Longitudinal)	12
3 Typical Tensile Stress-Strain Curves at Temperature for X2048-T851 Plate (Transverse)	13
4 Typical Compressive Stress-Strain and Tangent-Modulus Curves at Temperature for X2048-T851 Plate (Longitudinal)	14
5 Typical Compressive Stress-Strain and Tangent-Modulus Curves at Temperature for X2048-T851 Plate (Transverse)	15
6 Effect of Temperature on the Tensile Properties of X2048-T851 Plate	16
7 Effect of Temperature on the Compressive Properties of X2048-T851 Plate	16
8 Axial Load Fatigue Behavior of Unnotched X2048-T851 Plate (Longitudinal)	17
9 Axial Load Fatigue Behavior of Notched ($K_t = 3.0$) X2048-T851 Plate (Longitudinal)	17
10 Stress-Rupture Curves for X2048-T851 Plate (Longitudinal)	18
11 Specimen Layout for 7050-T73651 Plate	20
12 Typical Tensile Stress-Strain Curves at Temperature for 7050-T73651 Plate (Longitudinal)	29
13 Typical Tensile Stress-Strain Curves at Temperature for 7050-T73651 Plate (Transverse)	30
14 Typical Compressive Stress-Strain and Tangent-Modulus Curves at Temperature for 7050-T73651 Plate (Longitudinal)	31
15 Typical Compressive Stress-Strain and Tangent-Modulus Curves at Temperature for 7050-T73651 Plate (Transverse)	32
16 Effect of Temperature on the Tensile Properties of 7050-T73651 Plate	33
17 Effect of Temperature on the Compressive Properties of 7050-T73651 Plate	33

LIST OF ILLUSTRATIONS
(Continued)

		<u>Page</u>
Figure 18	Axial Load Fatigue Behavior of Unnotched 7050-T73651 Plate (Transverse)	34
19	Axial Load Fatigue Behavior of Notched ($K_t = 3.0$) 7050-T73651 Plate (Transverse)	34
20	Stress-Rupture and Plastic Deformation Curves for 7050-T73651 Plate (Transverse)	35
21	Specimen Layout for 21-6-9 Annealed Sheet	37
22	Typical Tensile Stress-Strain Curves at Temperature for 21-6-9 Annealed Sheet (Longitudinal)	45
23	Typical Tensile Stress-Strain Curves at Temperature for 21-6-9 Annealed Sheet (Transverse)	46
24	Typical Compressive Stress-Strain and Tangent-Modulus Curves at Temperature for 21-6-9 Annealed Sheet (Longitudinal)	47
25	Typical Compressive Stress-Strain and Tangent-Modulus Curves at Temperature for 21-6-9 Annealed Sheet (Transverse)	48
26	Effect of Temperature on the Tensile Properties of 21-6-9 Annealed Sheet	49
27	Effect of Temperature on the Compressive Properties of 21-6-9 Annealed Sheet	49
28	Axial Load Fatigue Behavior of Unnotched 21-6-9 Annealed Sheet (Transverse)	50
29	Axial Load Fatigue Behavior of Notched ($K_t = 3.0$) 21-6-9 Annealed Sheet (Transverse)	50
30	Stress-Rupture and Plastic Deformation Curves for 21-6-9 Annealed Sheet (Transverse)	51
31	Specimen Layout for Ti-8Mo-8V-2Fe-3Al Sheet	53
32	Typical Tensile Stress-Strain Curves at Temperature for Solution-Treated and Aged Ti-8Mo-8V-2Fe-3Al Sheet (Longitudinal)	61
33	Typical Tensile Stress-Strain Curves at Temperature for Solution-Treated and Aged Ti-8Mo-8V-2Fe-3Al Sheet (Transverse)	62
34	Typical Compressive Stress-Strain and Tangent-Modulus Curves at Temperature for Solution-Treated and Aged Ti-8Mo-8V-2Fe-3Al Sheet (Longitudinal)	63

LIST OF ILLUSTRATIONS
(Continued)

		<u>Page</u>
Figure 35	Typical Compressive Stress-Strain and Tangent-Modulus Curves at Temperature for Solution-Treated and Aged Ti-8Mo-8V-2Fe-3Al Sheet (Transverse)	64
36	Effect of Temperature on the Tensile Properties of Solution Treated and Aged Ti-8Mo-8V-2Fe-3Al Sheet	65
37	Effect of Temperature on the Compressive Properties of Solution Treated and Aged Ti-8Mo-8V-2Fe-3Al Sheet	65
38	Axial Load Fatigue Behavior of Unnotched Solution-Treated and Aged Ti-8Mo-8V-2Fe-3Al Sheet (Transverse)	66
39	Axial Load Fatigue Behavior of Notched ($K_t = 3.0$) Solution Treated and Aged Ti-8Mo-8V-2Fe-3Al Sheet (Transverse)	66
40	Stress-Rupture and Plastic Deformation Curves for Solution Treated and Aged Ti-8Mo-8V-2Fe-3Al Sheet (Transverse)	67
41	Specimen Layout for Ti-6Al-2Zr-2Sn-2Mo-2Cr Plate	69
42	Typical Tensile Stress-Strain Curves at Temperature for Solution Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Plate (Longitudinal)	78
43	Typical Tensile Stress-Strain Curves at Temperatures for Solution Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Plate (Transverse)	79
44	Typical Compressive Stress-Strain and Tangent-Modulus Curves for Solution Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Plate (Longitudinal)	80
45	Typical Compressive Stress-Strain and Tangent-Modulus Curves for Solution Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Plate (Transverse)	81
46	Effect of Temperature on the Tensile Properties of Solution Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Plate	82
47	Effect of Temperature on the Compressive Properties of Solution Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Plate	82
48	Axial Load Fatigue Behavior of Unnotched Solution Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Plate (Transverse)	83
49	Axial Load Fatigue Behavior of Notched ($K_t = 3.0$) Solution Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Plate (Transverse)	83

LIST OF ILLUSTRATIONS
(Continued)

		<u>Page</u>
Figure 50	Stress-Rupture and Plastic Deformation Curves for Solution Treated and Aged Ti-6Al-2Zr-2Sn-2Mo-2Cr Plate (Transverse) . . .	84
51	Typical Tensile Stress-Strain Curves for Solution Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings	93
52	Typical Compressive Stress-Strain and Tangent Modulus Curves for Solution Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings	94
53	Effect of Temperature on the Tensile Properties of Solution Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings	95
54	Effect of Temperature on the Compressive Properties of Solution Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings	95
55	Axial Load Fatigue Behavior of Unnotched Solution-Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings (Transverse)	96
56	Axial Load Fatigue Behavior of Notched ($K_t = 3.0$) Solution Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings (Transverse)	96
57	Stress Rupture and Plastic Deformation Curves for Solution Treated and Aged Ti-6Al-6V-2Sn Isothermal Die Forgings	97
58	Tensile Ultimate Strength as a Function of Temperature	99
59	Tensile Yield Strength as a Function of Temperature	100
60	Sheet and Thin-Plate Tensile Specimen	110
61	Round Tensile Specimen	110
62	Sheet Compression Specimen	110
63	Round Compression Specimen	110
64	Sheet Creep- and Stress-Rupture Specimen	110
65	Round Creep- and Stress-Rupture Specimen	110
66	Sheet Shear Test Specimen	111
67	Pin Shear Specimen	111
68	Unnotched Sheet Fatigue Specimen	111
69	Notched Sheet Fatigue Specimen	111

LIST OF ILLUSTRATIONS
(Continued)

	<u>Page</u>
Figure 70 Unnotched Round Fatigue Specimen	111
71 Notched Round Fatigue Specimen	111
72 Sheet Fracture Toughness Specimen	112
73 Slow Bend Fracture Toughness Specimen	112
74 Stress-Corrosion Specimen	112
75 Thermal-Expansion Specimen	112
76 Sheet Bend Specimen	112
77 Notched Impact Specimen	112

INTRODUCTION

The selection of materials to most effectively satisfy new environmental requirements and increased design load requirements for advanced Air Force weapons systems is of vital importance. A major difficulty that design engineers encounter, particularly for newly developed materials, materials processing, and product forms, is a lack of sufficient engineering data to effectively evaluate the relative potential of these developments for a particular application.

In recognition of this need, the Air Force has sponsored several programs at Battelle's Columbus Laboratories to provide comparative engineering data for newly developed materials. The materials included in these evaluation programs were carefully selected to insure that they were either available or could become quickly available on request and that they would represent potentially attractive alloy projections for weapons system usage. The results of these programs have been published in five technical reports, AFML-TR-67-418, AFML-TR-68-211, AFML-TR-70-252, AFML-TR-71-249, and AFML-TR-72-196, Volumes I and II.

This technical report is a result of the continuing effort to relieve the above situation and to stimulate interest in the use of newly developed alloys, or new processing techniques for older alloys, for advanced structures.

The materials evaluated under this program are as follows

- (1) X2048-T851 Plate
- (2) 7050-T73651 Plate
- (3) 21-6-9 Annealed Sheet
- (4) Ti-8Mo-8V-2Fe-3Al STA Sheet
- (5) Ti-6Al-2Zr-2Sn-2Mo-2Cr STA Plate
- (6) Ti-6Al-6V-2Sn STA Isothermal Die Forgings .

The temper or heat-treat conditions selected for evaluation are described in each alloy section.

The program approach was, as on previous contracts, to search the published literature and to contact metal producers and aerospace companies for any pertinent data. If very little pertinent information was available, a complete material evaluation was conducted. On this program a complete evaluation was conducted for each material. Upon completion of each evaluation, a "data sheet" was issued to make the information immediately available to potential users rather than defer publication to the end of the contract term and this summary technical report. These data sheets are reproduced as Appendix III of this report.

Detailed information concerning the properties of interest, test techniques, and specimen types are contained in Appendices I and II of this report.

X2048-T851 Aluminum AlloyMaterial Description

Alloy X2048-T851 is a recent development of the Reynolds Metals Company. The development aim was a thick section alloy with high toughness and stability at moderate temperatures. The goal was to achieve the strength, fatigue resistance, corrosion resistance, and thermal stability of 2024-T851 or 2124-T851 and the toughness of 2219.

The material used for this evaluation was 3-inch plate produced within the following composition limits

Copper	2.8 to 3.8
Manganese	0.20 to 0.60
Magnesium	1.2 to 1.8
Zinc	0.25 max
Titanium	0.10 max
Silicon	0.15 max
Iron	0.20 max
Others total	0.15 max
Aluminum	Balance

Processing and Heat Treating

Specimens were cut from the plate as shown in Figure 1 and were tested in the as-received -T851 temper.

Test Results

Tension. Test results for longitudinal and transverse specimens at room temperature, 250 F, 350 F, and 500 F are given in Table I. Short-transverse test results at room temperature only are also given in Table I. Stress-strain curves at temperature are shown in Figures 2 and 3. Effect-of-temperature curves are presented in Figure 6.

Compression. Results of tests in both the longitudinal and transverse directions at room temperature, 250 F, 350 F, and 500 F are given in Table II. Stress-strain and tangent-modulus curves at temperature are shown in Figures 4 and 5. Effect-of-temperature curves are presented in Figure 7.

Shear. Results of room temperature pin shear tests in both the longitudinal and transverse directions are given in Table III.

52	51	54	55	56	57	58	59	60	61	62	63	64	65	66	67	68	69	70	71	72	73	74	75	76	77	78	79	80	81	82	83	84	85	86	87	88	89	90	91	92	93	94	95	96	97	98	99	100	101	102	103	104	105	106	107	108	109	110	111	112	113	114	115	116	117	118	119	120	121	122	123	124	125	126	127	128	129	130	131	132	133	134	135	136
----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----

52	51	54	55	56	57	58	59	60	61	62	63	64	65	66	67	68	69	70	71	72	73	74	75	76	77	78	79	80	81	82	83	84	85	86	87	88	89	90	91	92	93	94	95	96	97	98	99	100	101	102	103	104	105	106	107	108	109	110	111	112	113	114	115	116	117	118	119	120	121	122	123	124	125	126	127	128	129	130	131	132	133	134	135	136
----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----	-----

FIGURE 1. SPECIMEN LAYOUT FOR X2048-T851 PLATE

Impact. Charpy V-notch test results for longitudinal and transverse specimens are given in Table IV.

Fracture Toughness. Results of slow-bend type tests in both the longitudinal (L-T) and transverse (T-L) directions are given in Table V. The specimens were 1.00-inch thick by 2.00-inches wide with a span of 8 inches. The candidate K_{IC} values shown in Table V are considered valid K_{IC} values by existing ASTM criteria. (Higher K_{IC} values may be achieved with larger specimens. Reference J. G. Kaufman, "Notes for E-24.01 Meeting", held at Battelle's Columbus Laboratories on October 4, 1972.)

Fatigue. Axial-load test results for longitudinal specimens at a ratio of $R = 0.1$ are given in Tables VI and VII. These tests were conducted for both unnotched and notched ($K_t = 3.0$) specimens at room temperature, 250 F, and 350 F. S-N curves are presented in Figures 8 and 9.

Creep and Stress-Rupture. Results of tests on longitudinal specimens at 250 F, 350 F, and 500 F are given in Table VIII. Log-stress versus log-time curves are presented in Figure 10.

Stress Corrosion. Specimens were tested as described in the experimental procedure section of this report. No cracks or failures occurred in the 1000-hour test duration.

Thermal Expansion. The coefficient of thermal expansion for this alloy was determined to be 12.9×10^{-6} in./in./F for 68 F to 350 F.

Density. The density of this material is 0.0994 lb./in.³.

TABLE I. TENSION TEST RESULTS FOR X2048-T851 ALUMINUM PLATE

Specimen Number	Ultimate Tensile Strength, ksi	0.2 Percent Offset Yield Strength, ksi	Elongation in 2 Inches, percent	Reduction in Area, percent	Tensile Modulus, 10 ⁶ psi
<u>Longitudinal at Room Temperature</u>					
1L-1	66.2	60.5	8.0	15.7	10.2
1L-2	66.2	60.3	8.5	15.8	10.3
1L-3	<u>66.4</u>	<u>60.4</u>	<u>8.5</u>	<u>15.5</u>	<u>10.2</u>
Average	66.5	60.4	8.3	15.7	10.2
<u>Transverse at Room Temperature</u>					
1T-1	69.4	62.4	8.0	12.5	10.8
1T-2	66.4	60.0	7.0	12.2	10.5
1T-3	<u>66.5</u>	<u>60.2</u>	<u>6.5</u>	<u>10.3</u>	<u>10.3</u>
Average	67.4	60.9	7.2	11.7	10.5
<u>Short Transverse at Room Temperature</u>					
1ST-1	67.6	59.6	7.0	11.4	11.1
1ST-2	67.4	59.0	6.0	7.8	11.2
1ST-3	<u>66.4</u>	<u>58.2</u>	<u>6.0</u>	<u>9.0</u>	<u>11.1</u>
Average	67.1	58.9	6.3	9.4	11.1
<u>Longitudinal at 250 F</u>					
1L-4	59.8	56.5	13.5	33.9	9.5
1L-5	60.5	57.0	12.5	28.4	9.9
1L-6	<u>60.1</u>	<u>57.0</u>	<u>12.0</u>	<u>32.6</u>	<u>10.4</u>
Average	60.1	56.8	12.7	31.6	9.9
<u>Transverse at 250 F</u>					
1T-4	60.4	56.5	11.5	26.3	10.0
1T-5	59.7	56.0	13.5	29.3	10.0
1T-6	<u>59.8</u>	<u>56.3</u>	<u>13.0</u>	<u>27.6</u>	<u>9.4</u>
Average	60.0	56.3	12.7	27.7	9.8
<u>Longitudinal at 350 F</u>					
1L-7	51.6	49.4	13.5	38.8	9.3
1L-8	51.4	49.1	14.5	38.1	9.3
1L-9	<u>51.1</u>	<u>48.8</u>	<u>14.5</u>	<u>35.0</u>	<u>9.4</u>
Average	51.4	49.4	14.2	37.3	9.3
<u>Transverse at 350 F</u>					
1T-7	50.5	48.7	17.0	35.1	9.3
1T-8	51.1	49.4	16.5	33.5	9.4
1T-9	<u>49.3</u>	<u>48.2</u>	<u>16.0</u>	<u>33.9</u>	<u>9.1</u>
Average	50.3	48.8	16.5	34.2	9.3
<u>Longitudinal at 500 F</u>					
1L-10	34.5	32.1	10.0	27.2	8.6
1L-11	33.7	31.8	8.5	21.6	8.5
1L-12	<u>33.7</u>	<u>31.3</u>	<u>10.0</u>	<u>21.5</u>	<u>7.9</u>
Average	34.0	31.7	9.5	23.4	8.3
<u>Transverse at 500 F</u>					
1T-10	32.3	30.5	10.0	14.7	7.5
1T-11	35.0	33.2	7.5	15.1	8.0
1T-12	<u>32.8</u>	<u>31.0</u>	<u>7.0</u>	<u>15.1</u>	<u>7.6</u>
	33.4	31.6	8.2	15.0	7.7

TABLE II. COMPRESSION TEST RESULTS FOR
X2048-T851 ALUMINUM PLATE

Specimen Number	0.2 Percent Offset Yield Strength, ksi	Compression Modulus, 10 ³ psi
<u>Longitudinal at Room Temperature</u>		
2L-1	62.0	11.4
2L-2	59.0	11.1
2L-3	61.6	11.5
Average	60.9	11.3
<u>Transverse at Room Temperature</u>		
2T-1	60.6	10.9
2T-2	61.2	11.1
2T-3	60.0	11.4
Average	60.6	11.1
<u>Longitudinal at 250 F</u>		
2L-4	56.2	10.1
2L-5	56.8	10.3
2L-6	57.0	10.3
Average	56.7	10.2
<u>Transverse at 250 F</u>		
2T-4	56.8	10.3
2T-5	56.8	10.3
2T-6	54.4	10.2
Average	56.0	10.3
<u>Longitudinal at 350 F</u>		
2L-7	51.7	9.8
2L-8	48.8	9.4
2L-9	51.3	9.6
Average	50.6	9.6
<u>Transverse at 350 F</u>		
2T-7	52.0	9.9
2T-8	50.3	9.7
2T-9	50.9	9.6
Average	51.1	9.7
<u>Longitudinal at 500 F</u>		
2L-10	35.0	9.6
2L-11	35.3	9.0
2L-12	35.3	9.7
Average	35.2	9.4
<u>Transverse at 500 F</u>		
2T-10	33.1	9.7
2T-11	32.5	9.9
2T-12	33.1	9.7
Average	32.9	9.7

TABLE III. SHEAR TEST RESULTS FOR X2048-T851
ALUMINUM PLATE AT ROOM TEMPERATURE

Specimen Number	Ultimate Shear Strength, ksi
<u>Longitudinal</u>	
4L-1	39.3
4L-2	39.0
4L-3	39.8
4L-4	39.3
Average	<u>39.3</u>
<u>Transverse</u>	
	39.5
4T-2	40.1
4T-3	38.8
4T-4	38.5
Average	<u>39.2</u>

TABLE IV. CHARPY V-NOTCH TEST RESULTS
FOR X2048-T851 ALUMINUM PLATE

Specimen Number	Energy, ft./lbs.
<u>Longitudinal</u>	
10-1L	7.0
10-2L	9.0
10-3L	7.0
10-4L	5.0
10-5L	9.0
10-6L	10.0
10-7L	6.5
Average	<u>8.9</u>
<u>Transverse</u>	
10-1T	4.0
10-2T	4.0
10-3T	5.0
10-4T	4.0
10-5T	5.0
10-6T	5.0
Average	<u>4.5</u>

TABLE V. RESULTS OF SLOW-BEND TYPE FRACTURE TOUGHNESS TESTS FOR X2048-T851 ALUMINUM PLATE

Specimen Number	W, inches	a, inches	T, inches	P, lbs	Span, inches	$f\left(\frac{a}{W}\right)$	K_Q (a)
<u>Transverse (T-L)</u>							
6-1T	2.00	0.903	1.00	4,500	8.0	2.294	29.20
6-2T	2.00	0.936	1.00	4,100	8.0	2.410	27.95
6-3T	2.00	0.946	1.00	4,350	8.0	2.448	30.12
6-4T	2.00	0.942	1.00	4,300	8.0	2.433	29.59
6-5T	2.00	0.911	1.00	4,350	8.0	2.321	28.56
6-6T	2.00	0.916	1.00	4,425	8.0	2.339	29.27
						Average	29.17
<u>Longitudinal (L-T)</u>							
6-1L	2.00	0.876	1.00	4,925	8.0	2.205	30.72
6-2L	2.00	0.903	1.00	4,950	8.0	2.294	32.12
6-3L	2.00	0.918	1.00	4,900	8.0	2.346	32.52
6-4L	2.00	0.947	1.00	5,075	8.0	2.452	35.19
6-5L	2.00	0.880	1.00	4,880	8.0	2.218	30.61
6-6L	2.00	0.920	1.00	4,950	8.0	2.353	32.94
						Average	32.35

(a) These candidate K_Q values do meet existing ASTM size and crack length criteria and are considered valid K_{Ic} numbers.

TABLE VI. AXIAL LOAD FATIGUE TEST RESULTS FOR X2048-T851 ALUMINUM PLATE (UNNOTCHED, R = 0.1) (LONGITUDINAL)

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-2	60.0	9,500
5-3	55.0	21,300
5-1	50.0	30,200
5-4	45.0	70,600
5-8	42.5	2,581,900
5-5	40.0	50,400
5-7	37.5	53,300
5-6	35.0	3,658,400
5-9	30.0	11,340,800(a)
<u>250 F</u>		
5-10	60.0	8,400
5-11	55.0	17,400
5-12	50.0	42,200
5-13	45.0	124,100
5-15	42.5	223,900
5-14	40.0	109,300
5-16	37.5	2,384,200
5-17	35.0	204,300
5-18	30.0	238,300(b)
5-19	25.0	11,538,190(a)
<u>350 F</u>		
5-20	60.0	100
5-24	50.0	28,100
5-22	45.0	33,700
5-25	42.5	97,800
5-21	40.0	177,900
5-26	37.5	212,300
5-23	35.0	2,851,600
5-27	30.0	256,800
5-28	25.0	14,461,900

(a) Did not fail.

(b) Failed at Radius.

TABLE VII. AXIAL LOAD FATIGUE RESULTS FOR X2048-T851
ALUMINUM PLATE (NOTCHED, $K_t = 3.0$,
 $R = 0.1$) (LONGITUDINAL)

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-31	40.0	7,500
5-32	30.0	21,600
5-34	25.0	44,700
5-36	22.5	107,400
5-33	20.0	247,500
5-35	17.5	2,646,500
5-37	15.0	14,621,000 ^(a)
<u>250 F</u>		
5-44	40.0	6,430
5-45	30.0	26,600
5-47	25.0	48,300
5-46	20.0	91,800
5-49	17.5	1,061,800
5-50	15.0	8,524,200
5-51	12.5	11,392,300 ^(a)
<u>350 F</u>		
5-38	40.0	6,100
5-39	30.0	15,400
5-41	25.0	43,800
5-40	20.0	128,400
5-42	17.5	243,600
5-43	15.0	509,000
5-52	12.5	4,744,700
5-53	10.0	13,384,100 ^(a)

(a) Did not fail.

TABLE VIII. SUMMARY DATA ON CREEP AND RUPTURE PROPERTIES FOR X2048-T851 ALUMINUM PLATE (LONGITUDINAL)

Specimen Number	Stress, ksi	Temper- ature, F	Hours to Indicated Creep Deformation, percent					Initial Strain, percent	Rupture Time, hours	Elongation in 2 in., percent	Reduction of Area, percent	Minimum Creep Rate, percent
			0.1	0.2	0.5	1.0	2.0					
			Hours to Indicated Creep Deformation, percent									
3-3	60	250	--	--	--	--	2.710	0.1	8.9	22.4	--	
3-4	50	"	0.15	0.50	3.1	11	0.674	77.8	7.4	26.4	0.037	
3-5	46	"	10	80	1150	1900 (a)	0.507	1363.2(b)	1.315	--	0.0004	
8-8	40	"	60	1375	5650 (a)	--	0.574	1325.4(b)	0.770	--	0.00007	
3-10	50	350	--	--	--	--	2.655	0.02	12.6	41.1	--	
3-12	42	"	0.17	1.0	5	17	0.541	34.8	5.9	10.1	0.055	
3-9	35	"	17	62	180	275	0.367	333.7	3.7	3.9	0.0023	
3-2	25	"	125	410	1475 (a)	3165 (a)	0.274	1033.1(b)	0.655	--	0.00028	
3-7	20	500	0.2	0.6	1.6	3.5	5.4	0.274	6.7	27.0	0.25	
3-1	10	500	12	52	160	277	0.141	416.6	14.1	54.5	0.0027	
3-6	6.5	"	105	310	1200 (a)	--	0.118	527.3(b)	0.397	--	0.00032	
3-11	4.5	"	200	1000	--	--	0.056	984.5(b)	0.255	--	0.00008	

(a) Estimate.

(b) Test discontinued.

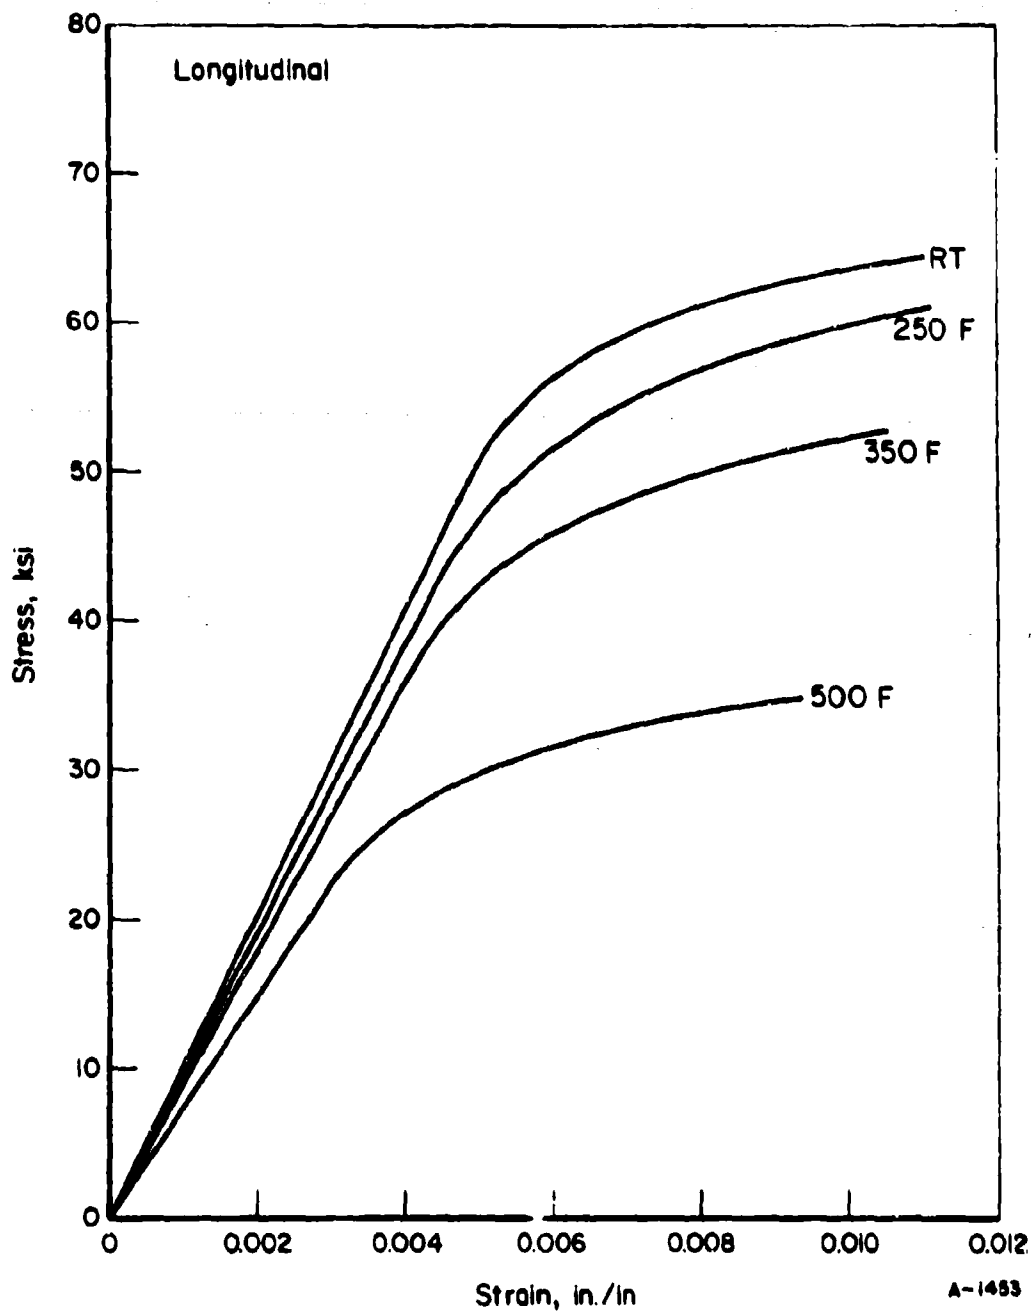


FIGURE 2. TYPICAL TENSILE STRESS-STRAIN CURVES AT TEMPERATURE FOR X2048-T851 PLATE (LONGITUDINAL.)

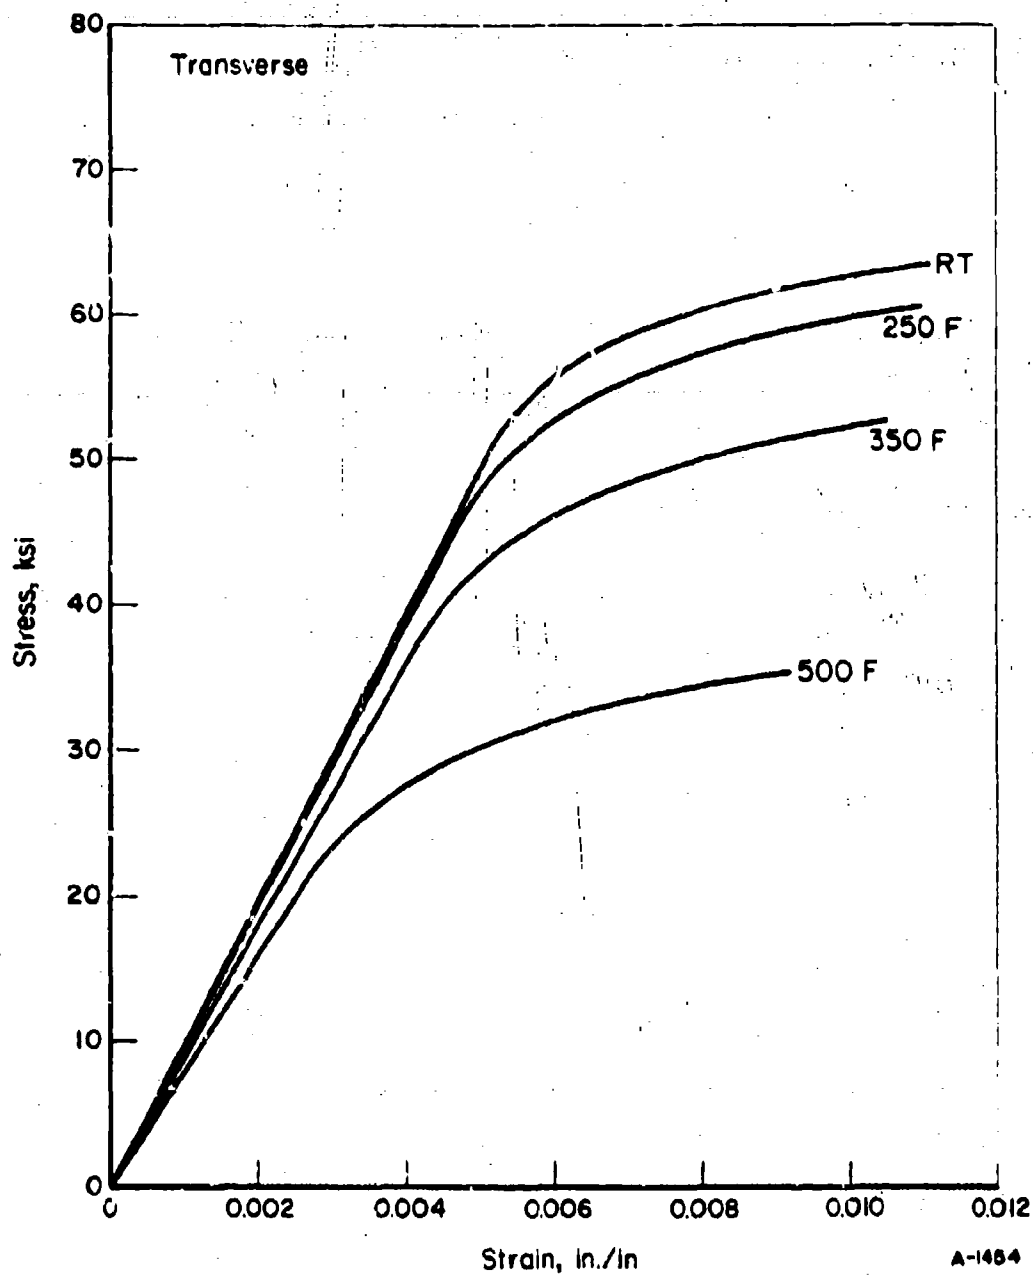


FIGURE 3. TYPICAL TENSILE STRESS-STRAIN CURVES AT TEMPERATURE FOR X2048-T851 PLATE (TRANSVERSE)

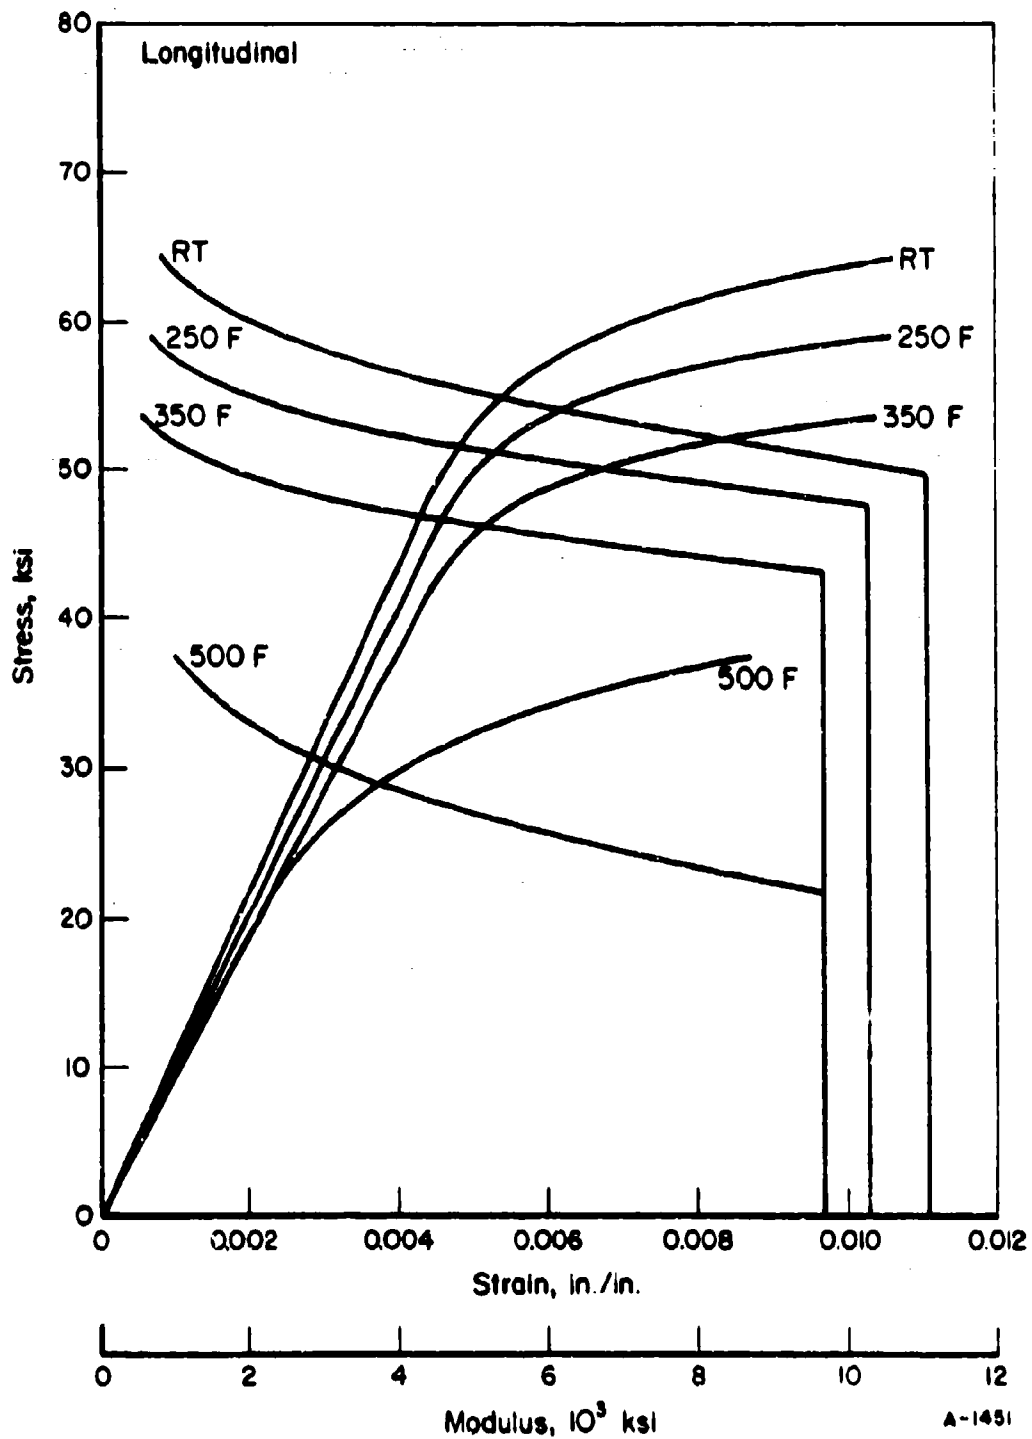


FIGURE 4. TYPICAL COMPRESSIVE STRESS-STRAIN AND TANGENT-MODULUS CURVES AT TEMPERATURE FOR X2048-T851 PLATE (LONGITUDINAL)

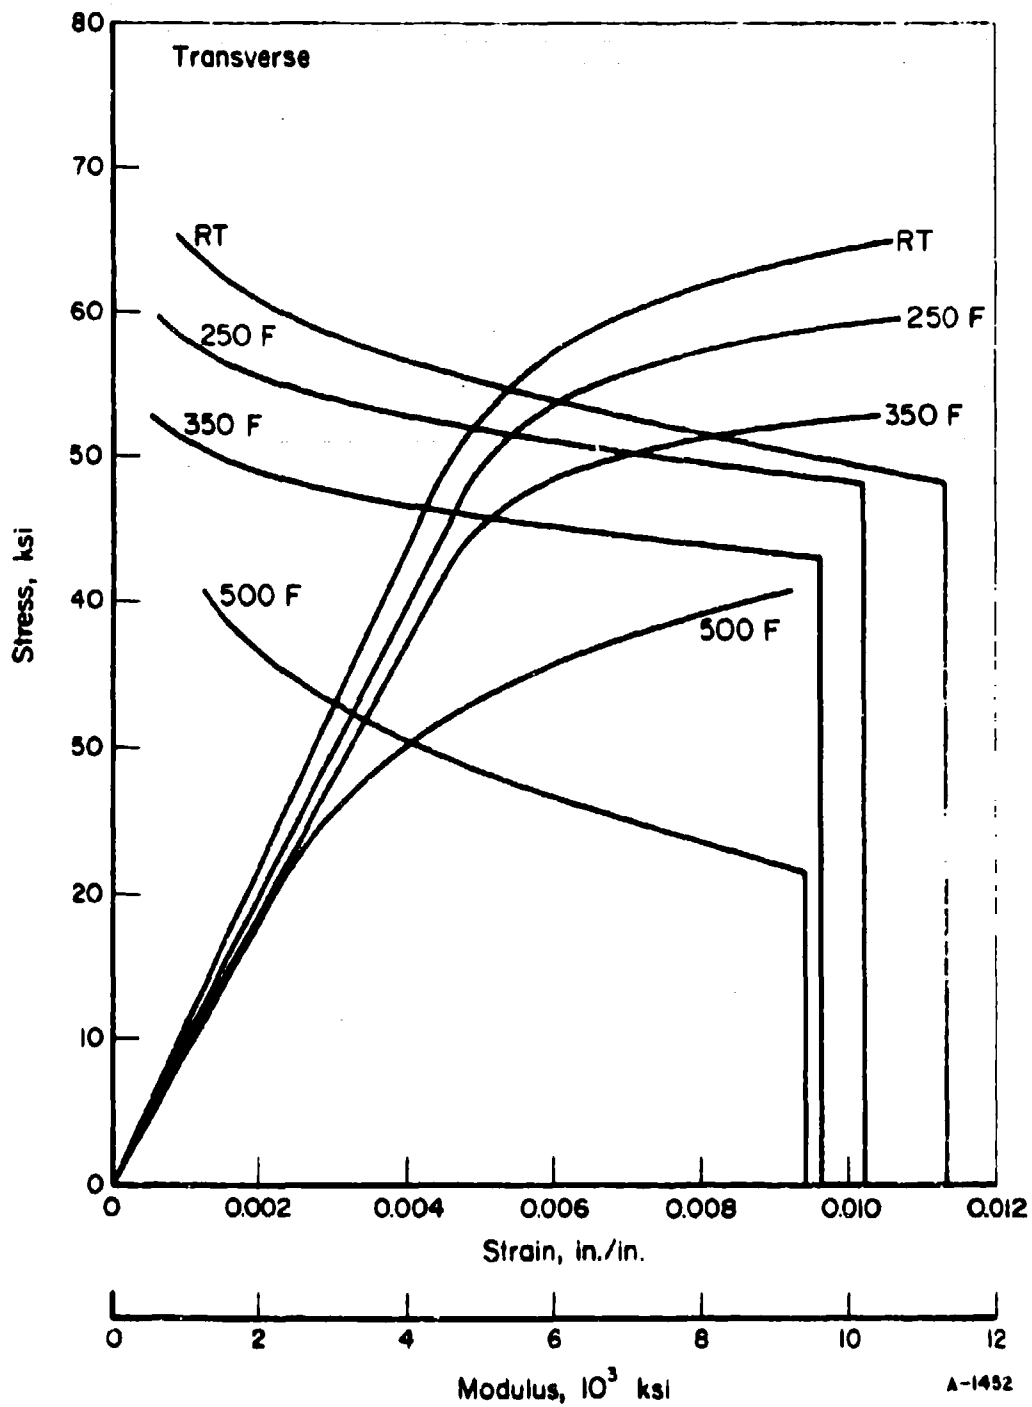


FIGURE 5. TYPICAL COMPRESSIVE STRESS-STRAIN AND TANGENT-MODULUS CURVES AT TEMPERATURE FOR X2048-T851 PLATE (TRANSVERSE)

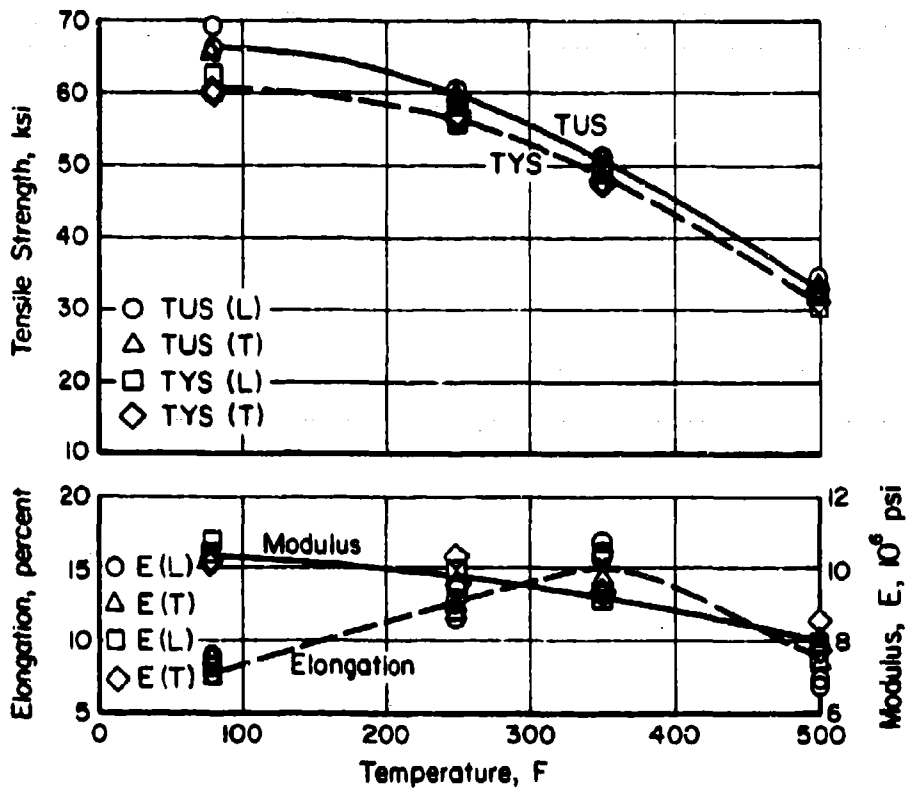


FIGURE 6. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF X2048-T851 PLATE

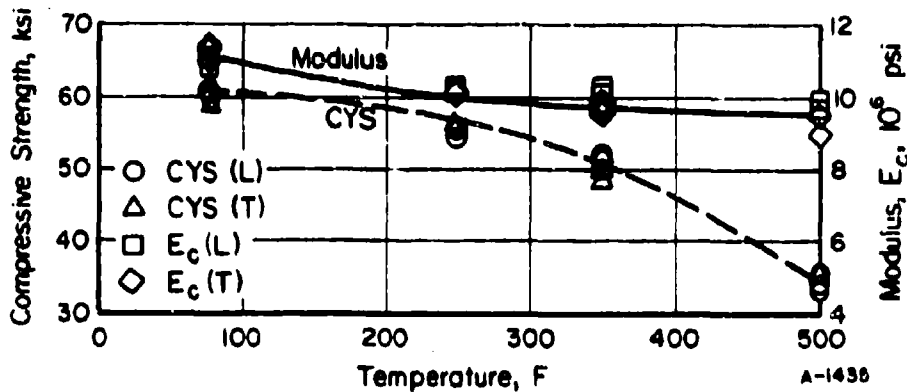


FIGURE 7. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF X2048-T851 PLATE

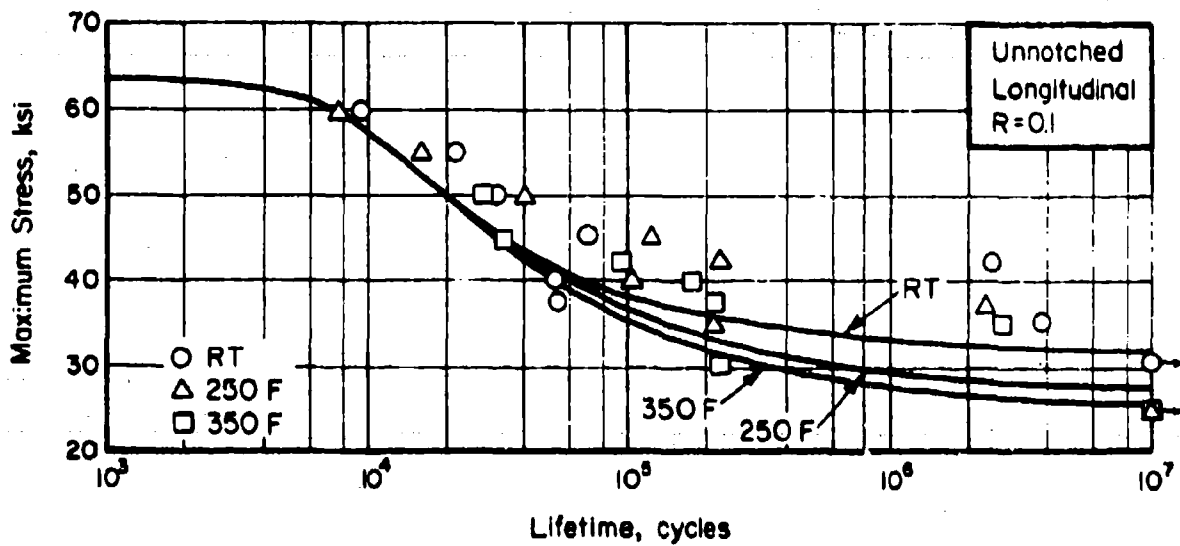


FIGURE 8. AXIAL LOAD FATIGUE BEHAVIOR OF UNNOTCHED X2048-T851 PLATE (LONGITUDINAL)

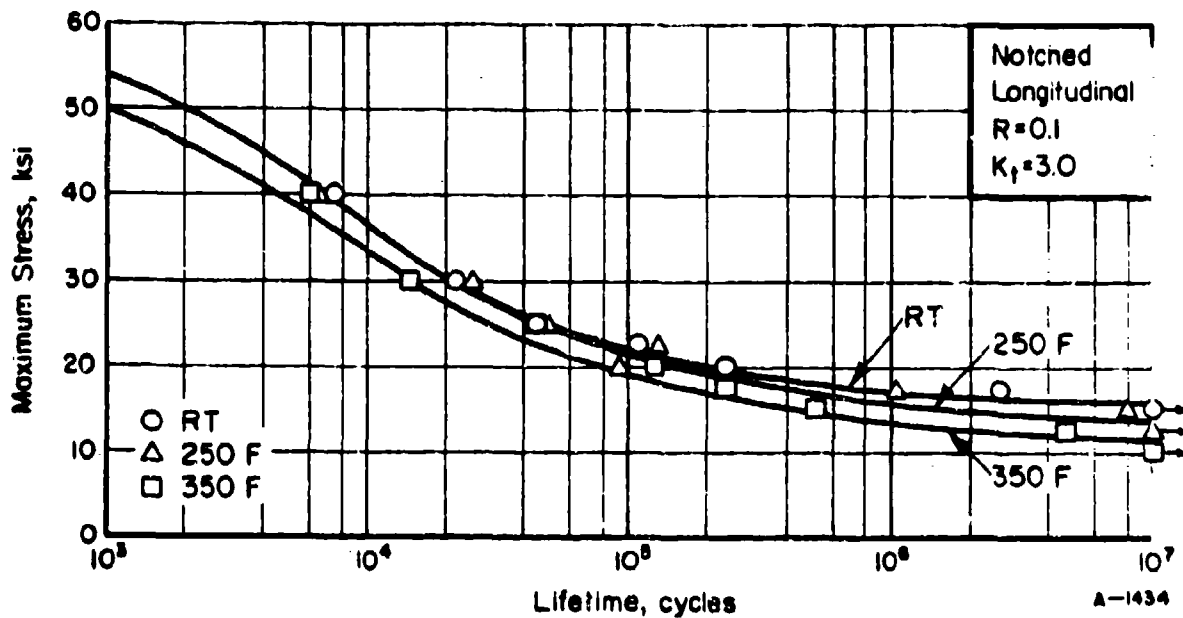


FIGURE 9. AXIAL LOAD FATIGUE BEHAVIOR OF NOTCHED ($K_t = 3.0$) X2048-T851 PLATE (LONGITUDINAL)

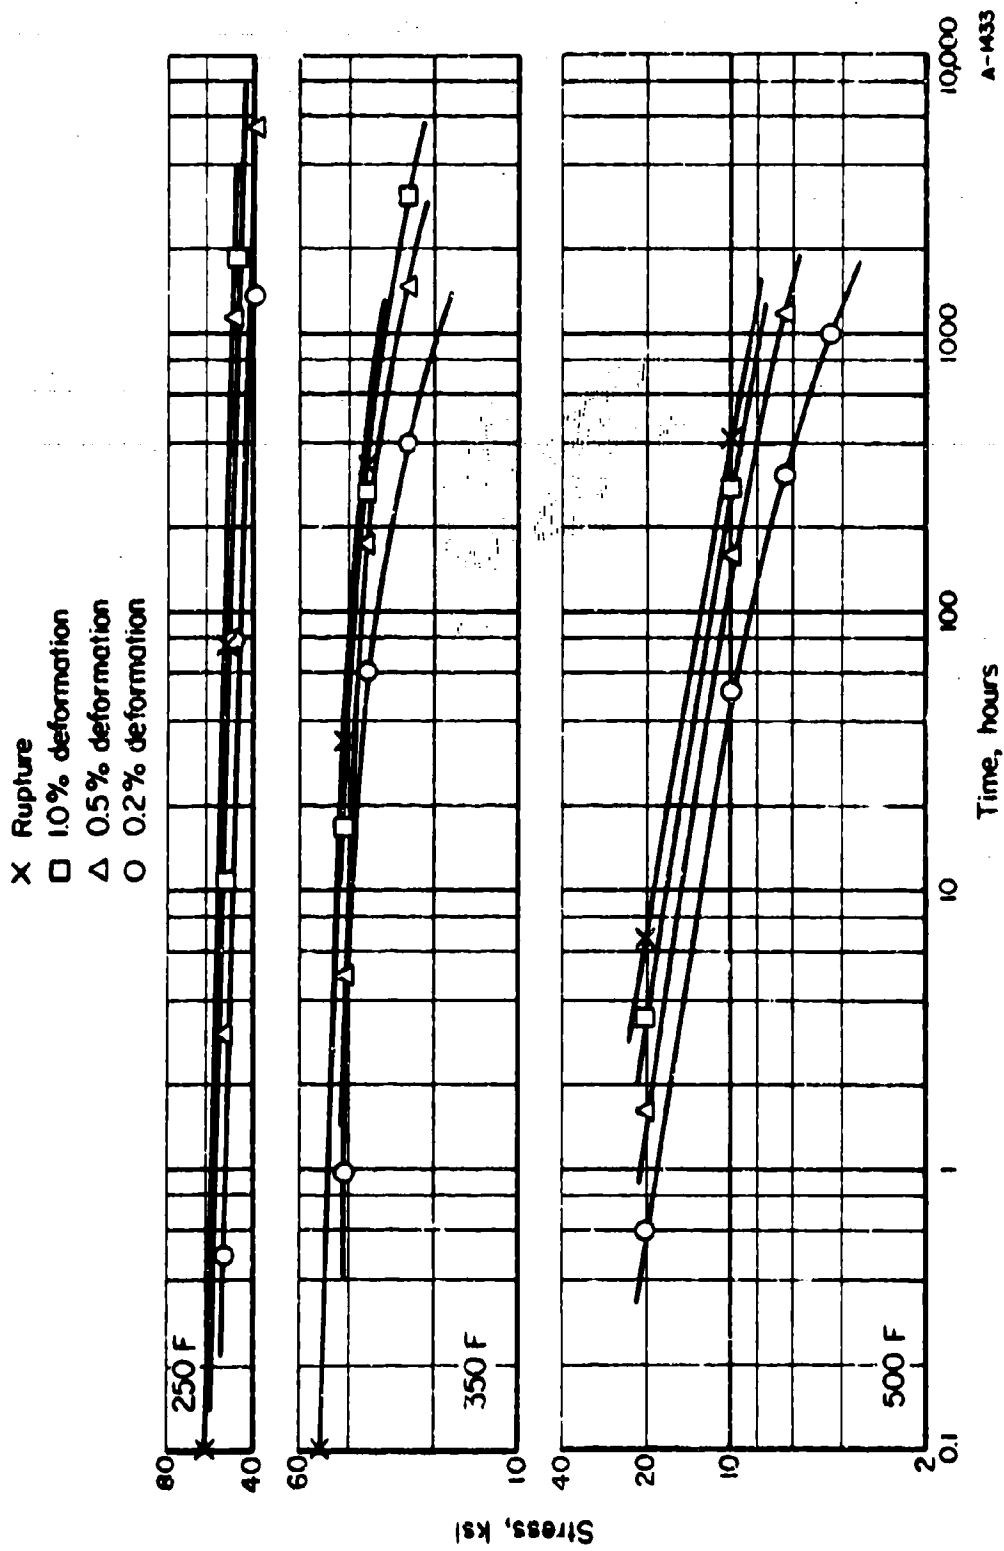


FIGURE 10. STRESS-RUPTURE AND PLASTIC DEFORMATION CURVES FOR X2048-T851 PLATE (LONGITUDINAL)

A-433

7050-T73651 Aluminum AlloyMaterial Description

Alloy 7050 is an Al-Zn-Mg-Cu alloy developed by the Alcoa Research Laboratories supported by the Naval Air Systems Command and the Air Force Materials Laboratory. When heat treated and aged to the -T73 temper, thick 7050 plate and hand forgings exhibit strengths equal to or exceeding those of 7079-T6XX products combined with improved fracture toughness and a high resistance to exfoliation and stress-corrosion cracking. The alloy differs from conventional 7XXX series aluminum alloys in that zirconium is added and chromium and manganese are restricted in order to minimize quench sensitivity.

The material used in this evaluation was 1-inch plate from Heat S-416420 produced within the following composition limits

Copper	2.0 to 2.8
Iron	0.15 max
Silicon	0.12 max
Manganese	0.10 max
Magnesium	1.9 to 2.6
Zinc	5.7 to 6.7
Chromium	0.04 max
Titanium	0.06 max
Aluminum	Balance .

Processing and Heat Treating

The specimen layout is shown in Figure 11. Specimens were tested in the as-received -T73651 temper.

Test Results

Tension. Test results for both longitudinal and transverse specimens at room temperature, 250 F, 350 F, and 500 F are given in Table IX. Typical stress-strain curves at temperature are presented in Figures 12 and 13. Effect-of-temperature curves are shown in Figure 16.

Compression. Test results for longitudinal and transverse specimens at room temperature, 250 F, 350 F, and 500 F are given in Table X. Typical stress-strain and tangent-modulus curves at temperature are presented in Figures 14 and 15. Effect-of-temperature curves are shown in Figure 17.

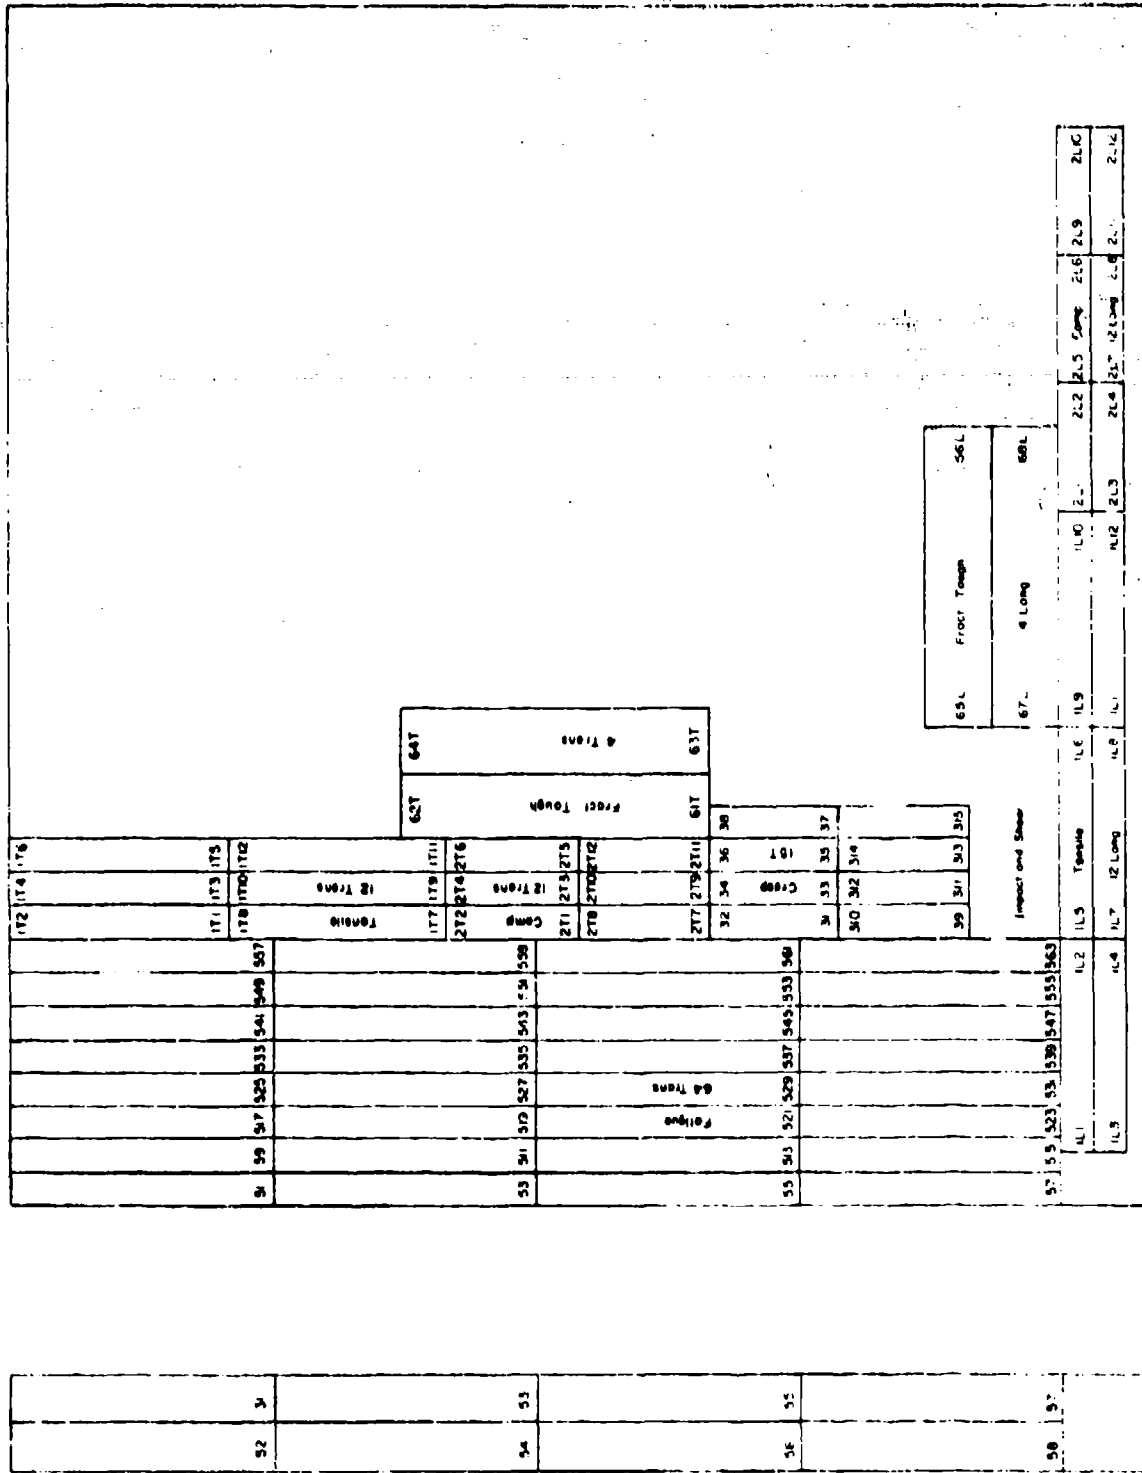


FIGURE 11. SPECIMEN LAYOUT FOR 7050-T73651 PLATE

Shear. Results of pin-type shear tests for longitudinal and transverse specimens at room temperature are given in Table XI.

Impact. Charpy V-notch test results for longitudinal and transverse specimens at room temperature are presented in Table XII.

Fracture Toughness. Results of slow-bend type tests in both the longitudinal (L-T) and transverse (T-L) directions are given in Table XIII. The candidate K_Q values shown in the Table are considered valid K_{Ic} values by existing ASTM criteria.

Fatigue. Axial load fatigue test results at a stress ratio of $R = 0.1$ are given in Tables XIV and XV for unnotched and notched transverse specimens. These tests were conducted at room temperature, 250 F, and 350 F. S-N curves are presented in Figures 18 and 19.

Creep and Stress-Rupture. Tests were conducted at 250 F, 350 F, and 500 F on transverse specimens. Tabular test results are given in Table XVI. Log-stress versus log-time curves are presented in Figure 20.

Stress Corrosion. Tests were performed as described in the experimental procedures section of this report. No failures or cracks occurred in the 1000 hour test duration.

Thermal Expansion. The coefficient of thermal expansion for this alloy is 12.8×10^{-6} in./in./F from 68 F to 212 F.

Density. The density of this material is 0.102 lb./in.³.

TABLE IX. TENSION TEST RESULTS FOR 7050-T73651
ALUMINUM ALLOY PLATE

Specimen Number	Ultimate Tensile Strength, ksi	0.2 Percent Offset Yield Strength, ksi	Elongation in 2 Inches, percent	Reduction in Area, percent	Tensile Modulus, 10 ⁴ psi
<u>Longitudinal at Room Temperature</u>					
1L-1	82.1	73.4	12.0	30.8	10.3
1L-2	82.9	74.0	12.0	30.0	10.4
1L-3	82.8	73.9	11.5	29.9	10.1
Average	82.6	73.8	11.8	30.2	10.3
<u>Transverse at Room Temperature</u>					
1T-1	81.4	72.4	10.0	23.3	10.6
1T-2	81.4	72.7	10.5	25.2	10.5
1T-3	81.7	72.6	11.0	24.9	10.4
Average	81.5	72.5	10.5	24.5	10.5
<u>Longitudinal at 250 F</u>					
1L-4	65.1	65.0	15.5	47.6	9.3
1L-5	64.8	64.8	15.5	48.2	9.4
1L-6	65.2	65.2	15.5	48.5	9.5
Average	65.0	64.9	15.5	48.1	9.4
<u>Transverse at 250 F</u>					
1T-4	64.4	63.8	13.5	39.1	9.3
1T-5	64.6	64.2	13.5	40.3	10.1
1T-6	64.5	64.2	13.0	36.8	9.7
Average	64.5	64.1	13.3	38.7	9.7
<u>Longitudinal at 350 F</u>					
1L-7	52.7	52.3	17.0	58.8	8.8
1L-8	54.6	54.4	16.5	57.2	8.4
1L-9	54.0	54.0	17.0	58.3	8.9
Average	53.7	53.5	16.8	58.1	8.7
<u>Transverse at 350 F</u>					
1T-7	53.0	52.8	14.5	48.8	3.9
1T-8	53.2	52.8	15.0	47.5	8.1
1T-9	54.3	54.3	14.5	47.2	9.1
Average	53.5	53.3	14.7	47.8	8.7
<u>Longitudinal at 500 F</u>					
1L-10	21.6	21.2	25.0	80.3	8.4
1L-11	22.2	21.8	22.0	79.8	8.1
1L-12	19.9	19.7	24.5	83.0	8.7
Average	21.2	20.9	23.8	81.0	8.4
<u>Transverse at 500 F</u>					
1T-10	19.9	19.7	23.0	80.8	8.5
1T-11	23.5	23.5	22.5	75.4	8.6
1T-12	19.4	19.4	25.0	83.2	8.8
Average	20.9	20.8	23.5	79.8	8.7

TABLE X. COMPRESSION TEST RESULTS FOR
7050-T73651 ALUMINUM ALLOY PLATE

Specimen Number	0.2 Percent Offset Yield Strength, ksi	Compressive Modulus, 10 ³ psi
<u>Longitudinal at Room Temperature</u>		
2L-1	73.1	10.8
2L-2	73.3	10.8
2L-3	72.7	10.8
Average	73.0	10.8
<u>Transverse at Room Temperature</u>		
2T-1	75.4	11.2
2T-2	75.2	10.9
2T-3	73.2	11.0
Average	75.3	11.0
<u>Longitudinal at 250 F</u>		
2L-4	64.4	9.5
2L-5	64.8	9.6
2L-6	63.7	9.4
Average	64.3	9.5
<u>Transverse at 250 F</u>		
2T-4	66.4	10.0
2T-5	66.1	9.9
2T-6	65.7	10.1
Average	66.1	10.0
<u>Longitudinal at 350 F</u>		
2L-7	54.2	9.0
2L-8	54.7	9.0
2L-9	52.1	9.1
Average	53.7	9.1
<u>Transverse at 350 F</u>		
2T-7	54.8	9.4
2T-8	54.8	9.6
2T-9	52.1	9.3
Average	55.1	9.4
<u>Longitudinal at 500 F</u>		
2L-10	20.1	8.5
2L-11	21.2	7.9
2L-12	21.3	7.8
Average	20.9	8.1
<u>Transverse at 500 F</u>		
2T-10	22.6	8.2
2T-11	21.0	7.9
2T-12	22.5	8.0
Average	22.0	8.0

TABLE XI. SHEAR TEST RESULTS FOR 7050-T73651 ALUMINUM ALLOY PLATE AT ROOM TEMPERATURE

Specimen Number	Ultimate Shear Strength, ksi
<u>Longitudinal</u>	
4L-1	46.8
4L-2	46.5
4L-3	50.2
4L-4	51.3
Average	<u>48.7</u>
<u>Transverse</u>	
4T-1	47.5
4T-2	47.9
4T-3	48.2
4T-4	43.3
Average	<u>47.9</u>

TABLE XII. IMPACT TEST RESULTS FOR 7050-T73651 ALUMINUM ALLOY PLATE AT ROOM TEMPERATURE

Specimen Number	Energy, ft. lbs.
<u>Longitudinal</u>	
10L-1	26.5
10L-2	44.0
10L-3	29.0
10L-4	57.0
10L-5	22.0
10L-6	30.0
Average	<u>34.7</u>
<u>Transverse</u>	
10T-1	6.0
10T-2	6.0
10T-3	5.5
10T-4	6.0
10T-5	5.5
10T-6	5.0
Average	<u>5.7</u>

TABLE XIII. RESULTS OF SLOW-BEND TYPE FRACTURE TOUGHNESS TESTS FOR 7050-T73651 ALUMINUM ALLOY PLATE

Specimen Number	w, inches	a, inches	T, inches	P, lbs.	Span, inches	$f(\frac{a}{w})$	$K_Q^{(a)}$
<u>Longitudinal (L-T)</u>							
6-1L	2.00	1.00	1.00	5,000	8.0	2.664	37.68
6-2L	2.00	0.990	1.00	5,100	8.0	2.622	37.83
6-3L	2.00	0.992	1.00	4,950	8.0	2.622	36.35
6-4L	2.00	1.01	1.00	5,100	8.0	2.708	39.07
6-5L	2.00	1.00	1.00	5,000	8.0	2.664	37.68
6-6L	2.00	0.964	1.00	5,190	8.0	2.508	36.90
Average							37.68
<u>(Transverse (T-L))</u>							
6-1T	2.00	0.963	1.00	5,200	8.0	2.510	36.90
6-2T	2.00	0.963	1.00	5,200	8.0	2.510	36.90
6-3T	2.00	1.00	1.00	5,000	8.0	2.663	37.70
6-4T	2.00	0.997	1.00	4,900	8.0	2.652	36.75
6-5T	2.00	0.990	1.00	4,900	8.0	2.623	36.30
6-6T	2.00	0.978	1.00	5,200	8.0	2.573	37.80
Average							36.99

(a) These candidate K_Q values do meet existing ASTM size and crack length criteria and are considered valid K_{Ic} numbers.

TABLE XIV. AXIAL LOAD FATIGUE TEST RESULTS FOR UNNOTCHED
7050-T73651 ALUMINUM PLATE (TRANSVERSE)

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-7	60.0	11,580
5-6	50.0	46,700
5-5	46.0	55,420
5-1	40.0	84,500
5-3	37.5	296,600
5-2	35.0	4,527,400
5-4	30.0	12,500,000 ^(a)
<u>250 F</u>		
5-16	60.0	9,390
5-14	50.0	21,680
5-13	45.0	29,390
5-9	40.0	77,100
5-10	37.5	133,200
5-11	35.0	99,900
5-25	32.5	1,086,400
5-8	30.0	363,800
5-15	25.0	443,400
5-22	20.0	10,151,300 ^(a)
<u>350 F</u>		
5-17	60.0	220
5-19	50.0	26,350
5-20	45.0	60,460
5-18	40.0	83,690
5-21	35.0	88,990
5-23	30.0	401,600
5-24	25.0	10,604,650 ^(a)

(a) Did not fail.

TABLE XV. AXIAL LOAD FATIGUE TEST RESULTS FOR NOTCHED
($K_t=3.0$) 7050-T73651 ALUMINUM PLATE (TRANSVERSE)

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-32	37.5	11,500
5-31	35.0	15,600
5-33	32.5	14,800
5-34	30.0	21,900
5-36	27.5	25,400
5-35	25.0	42,200
5-37	20.0	70,800
5-38	15.0	363,800
5-39	10.0	10,480,000 ^(a)
<u>250 F</u>		
5-40	37.5	7,200
5-41	35.0	13,000
5-42	32.5	14,400
5-43	30.0	17,100
5-44	25.0	36,900
5-46	20.0	127,300
5-45	15.0	293,600
5-47	10.0	10,000,480 ^(a)
<u>350 F</u>		
5-48	37.5	3,670
5-49	35.0	8,190
5-50	32.5	43,510
5-51	30.0	42,450
5-52	25.0	87,300
5-53	20.0	89,950
5-54	15.0	521,300
5-55	10.0	12,237,900 ^(a)

(a) Did not fail.

TABLE XVI. SUMMARY DATA ON CREEP AND RUPTURE PROPERTIES FOR 7050 ALUMINUM PLATE (TRANSVERSE)

Specimen Number	Stress, ksi	Temperature, F	Hours to Indicated Creep Deformation						Initial Strain, percent	Rupture Time, hours	Elongation		Reduction of Area, percent	Minimum Creep Rate, percent
			Percent								inches	percent		
			0.1	0.2	0.5	1.0	2.0	2.0						
3-10	60	250	0.04	0.07	0.18	0.38	0.85	0.803	3.9	15.2	43.2	1.35		
3-1	50	250	30	70	195	305 (a)	415	0.553	472.5 (b)	9.8	46.1	0.0125		
3-11	45	250	15	110 (a)	605 (a)	900	--	0.504	576.1 (b)	0.993	--	0.00053		
3-13	35	250	425	2700	8700	--	--	0.315	1007.3	0.432	--	0.00005		
3-4	45	350	0.02	0.03	0.07	0.13	0.22	0.603	0.4	16.7	40.5	7.2		
3-10	32	350	1.5	3.8	6.9	10	--	0.405	13.0	14.4	63.5	0.041		
3-2	25	350	11	43	103	133	145	0.306	135.1	17.4	70.4	0.0031		
3-8	20	350	35	30	305	420	490	0.315	502.7 (b)	21.2	76.9	0.0011		
3-12	12	350	675	1600 (a)	4800 (a)	--	--	0.156	1028.9	0.317	--	0.000095		
3-5	12	500	0.01	0.02	0.06	0.1	0.19	0.303	0.4	25.0	89.5	10.0		
3-7	9	500	3	8.5	14.3	23.6	29.5	0.155	37.7	25.7	87.6	0.034		
3-3	7	500	6	15	40	70	101	0.121	139.9	25.8	91.2	0.011		
3-14	5	500	10	40	220	525 (a)	775	0.102	1126.9 (b)	26.5	91.0	0.0014		
3-9	4	500	25	320	910	1550 (a)	--	0.045	1148.0	0.720	--	0.00001		

(a) Estimated.

(b) Test discontinued.

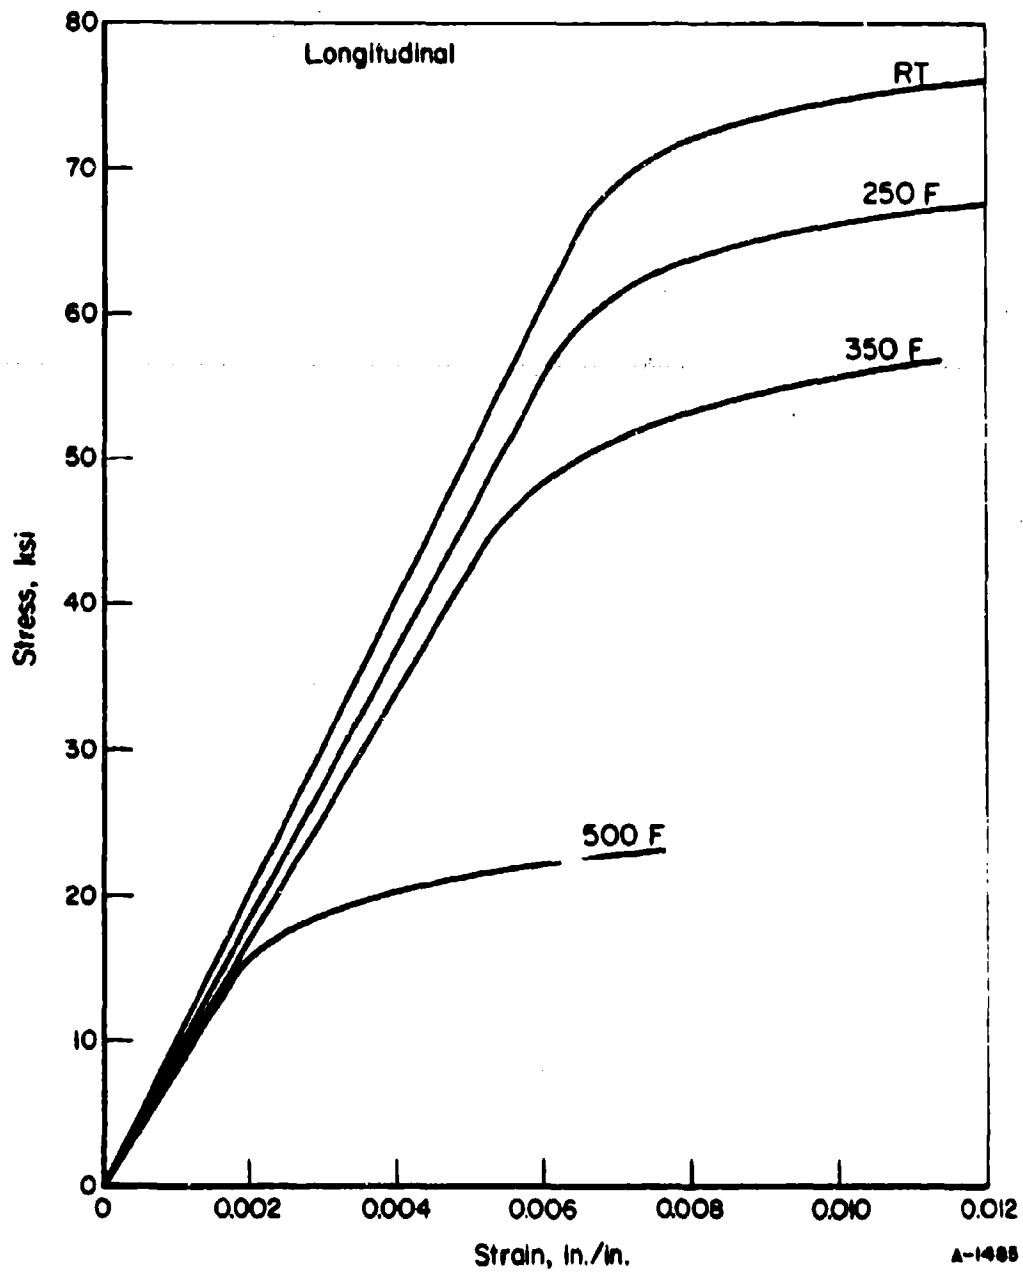


FIGURE 12. TYPICAL TENSILE STRESS-STRAIN CURVES AT TEMPERATURE FOR 7050-T73651 PLATE (LONGITUDINAL)

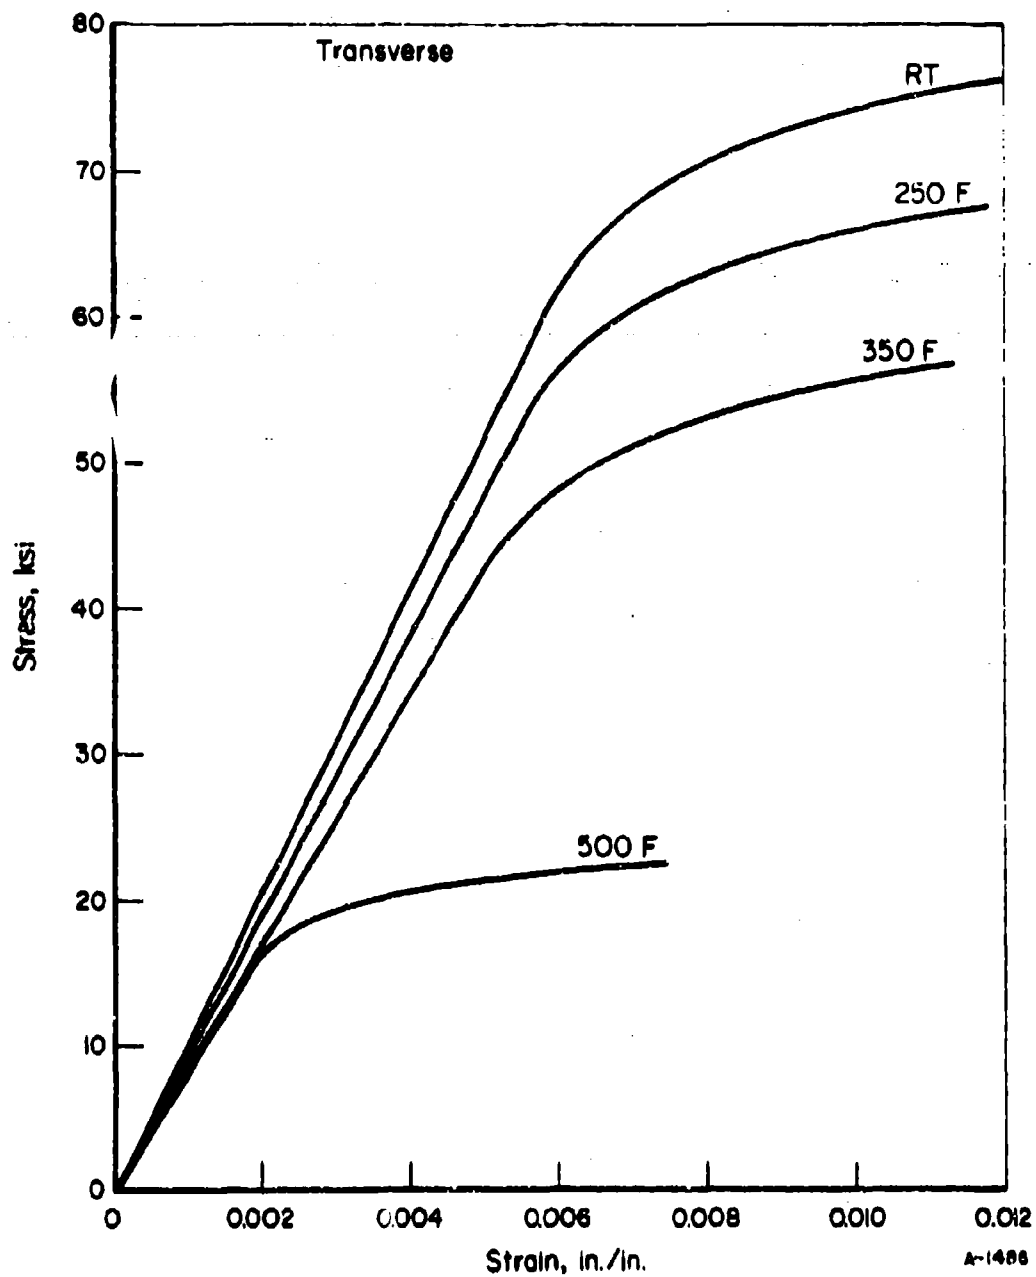


FIGURE 13. TYPICAL TENSILE STRESS-STRAIN CURVES AT TEMPERATURE FOR 7050-T73651 PLATE (TRANSVERSE)

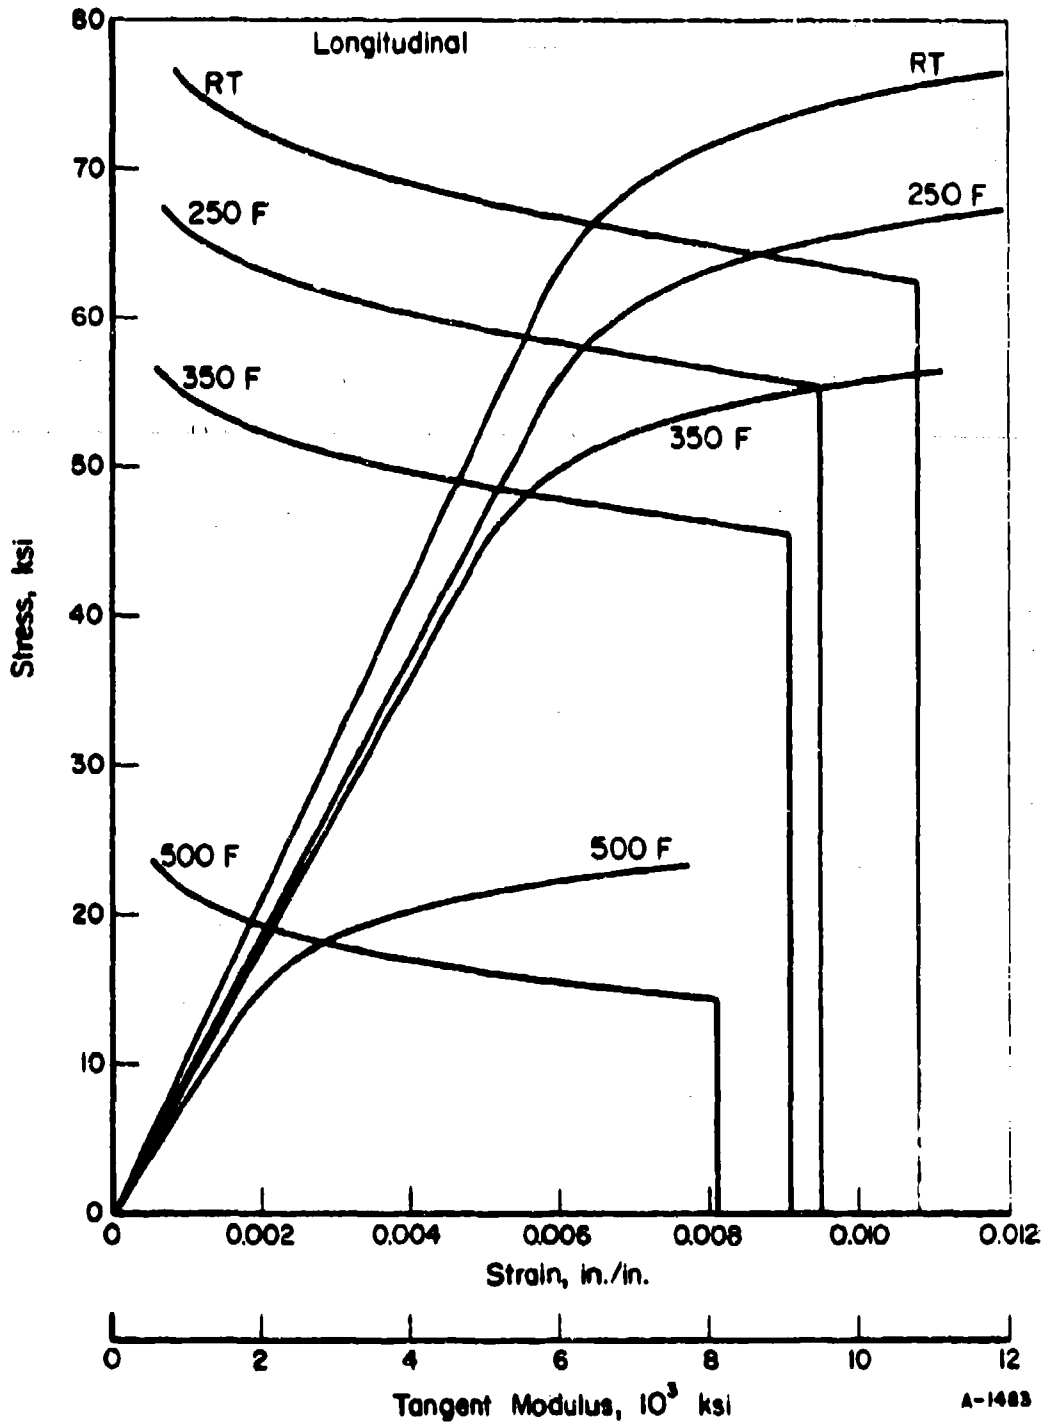


FIGURE 14. TYPICAL COMPRESSIVE STRESS-STRAIN AND TANGENT-MODULUS CURVES AT TEMPERATURE FOR 7050-T73651 PLATE (LONGITUDINAL)

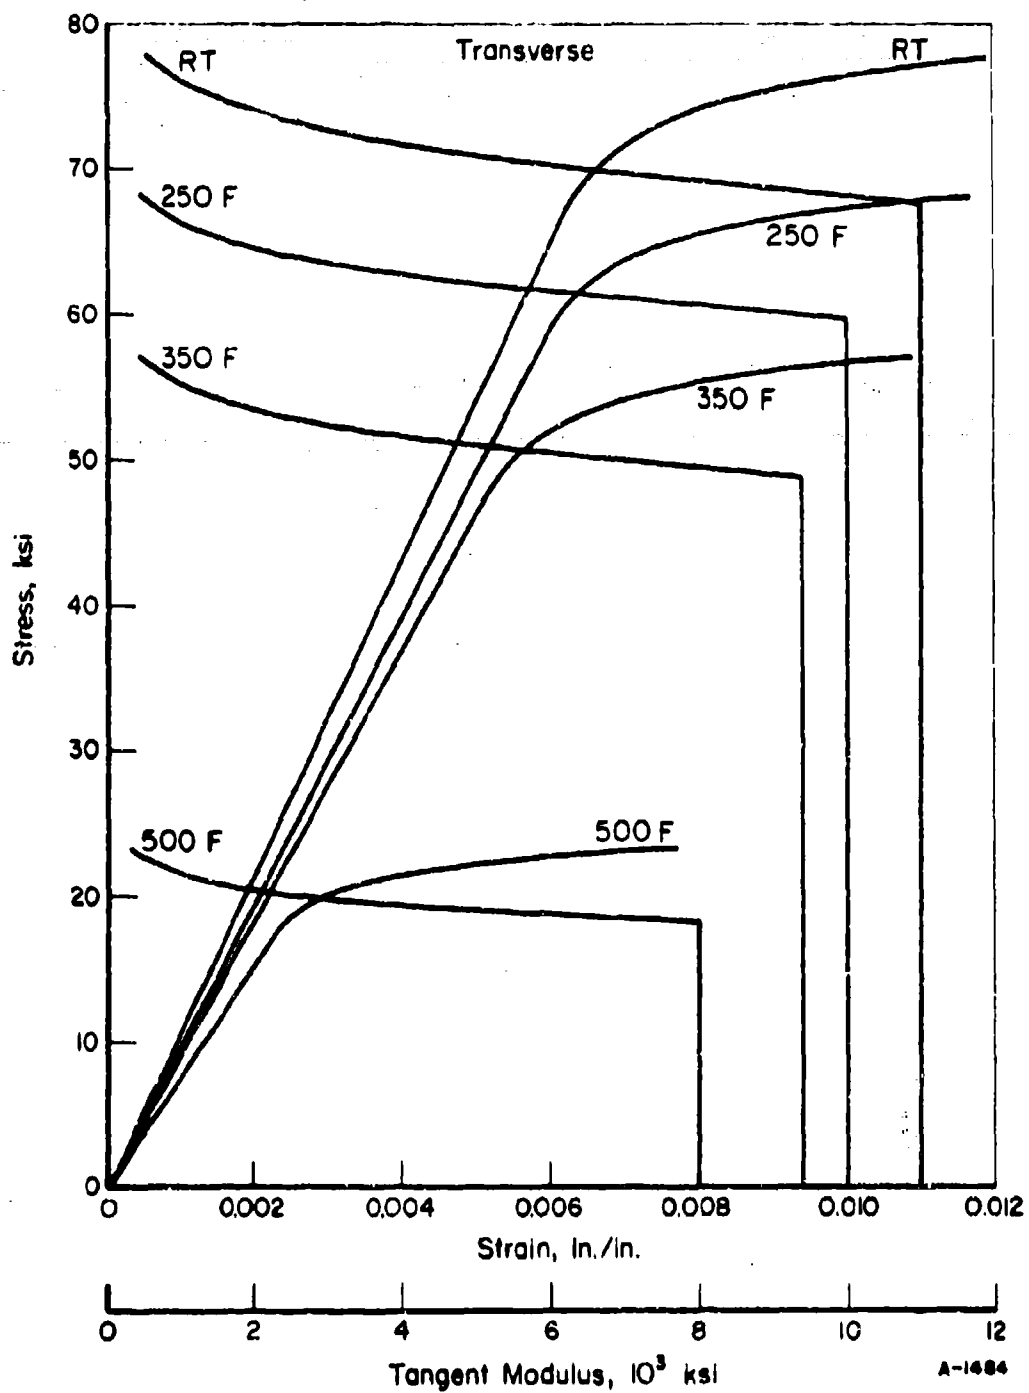


FIGURE 15. TYPICAL COMPRESSIVE STRESS-STRAIN AND TANGENT-MODULUS CURVES AT TEMPERATURE FOR 7050-T73651 PLATE (TRANSVERSE)

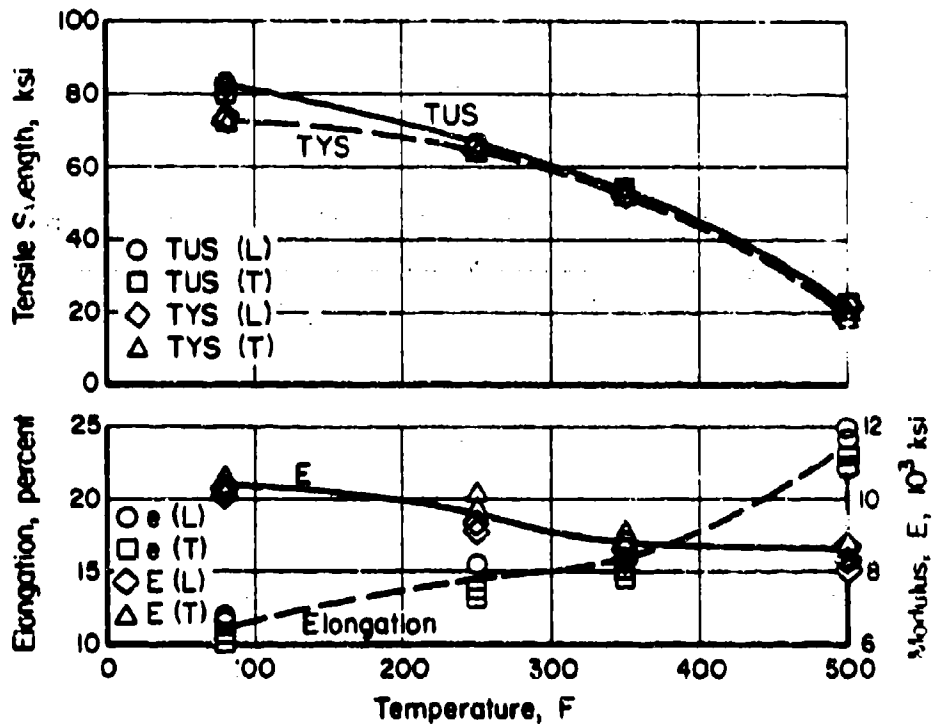


FIGURE 16. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF 7050-T73651 PLATE

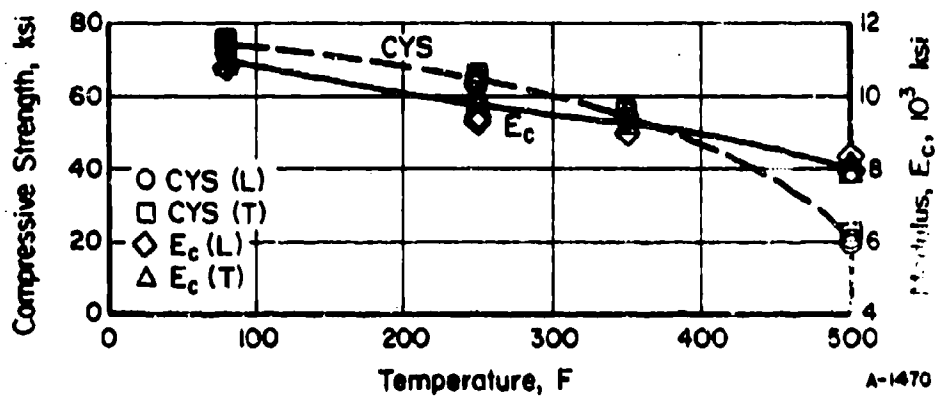


FIGURE 17. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF 7050-T73651 PLATE

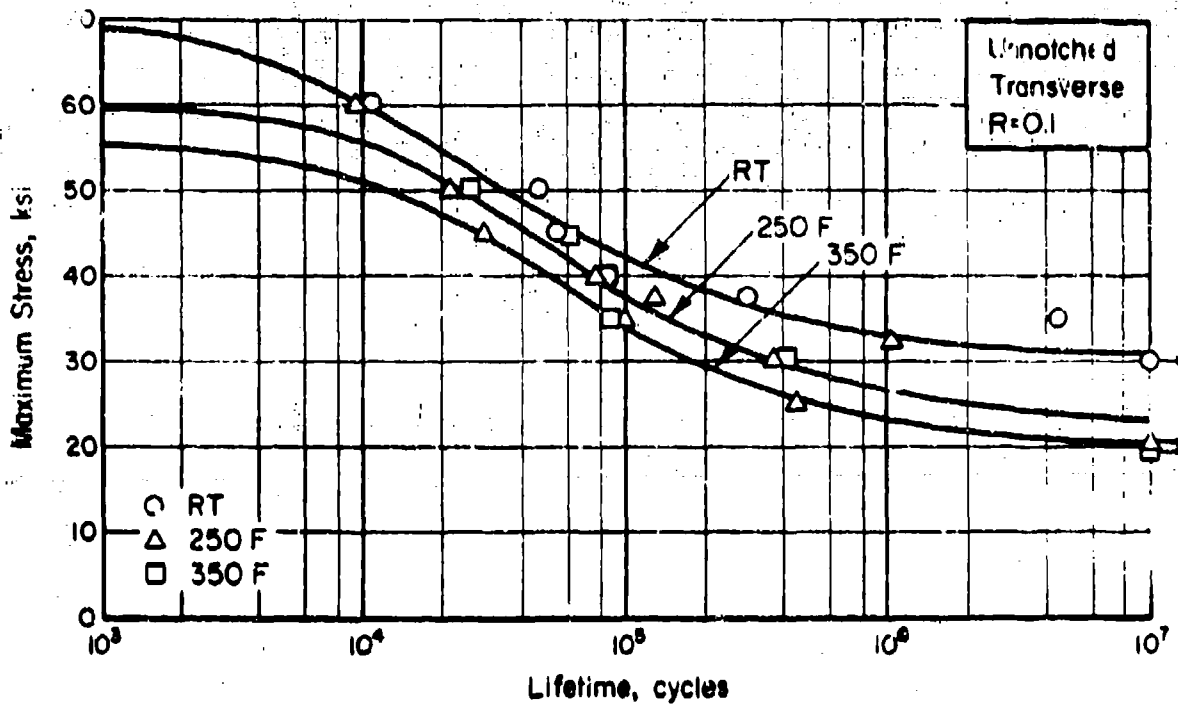


FIGURE 18. AXIAL LOAD FATIGUE BEHAVIOR OF UNNOTCHED 7050-T73651 PLATE (TRANSVERSE)

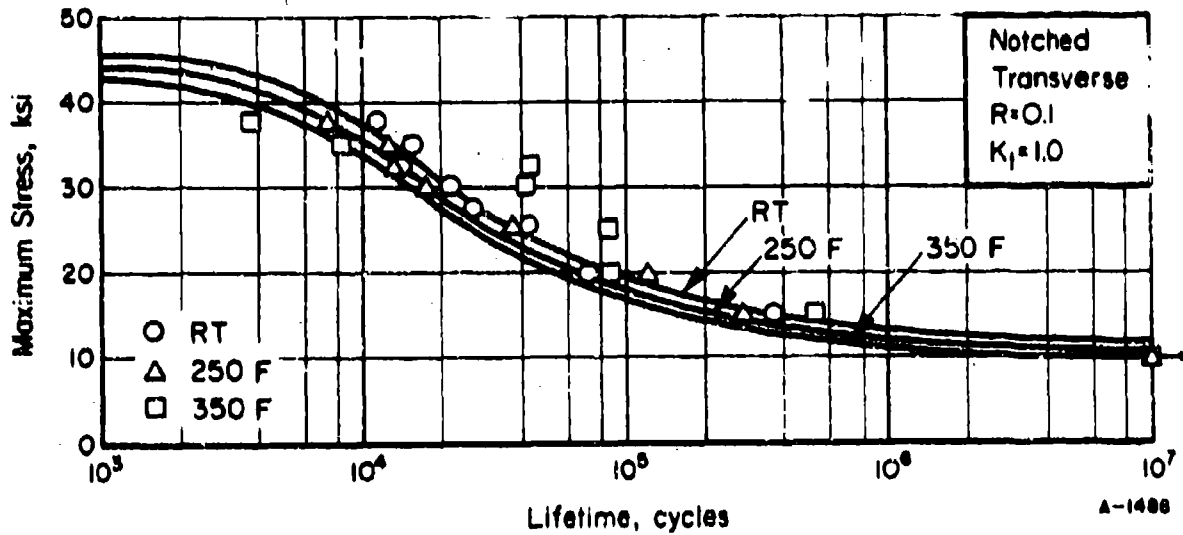


FIGURE 19. AXIAL LOAD FATIGUE BEHAVIOR OF NOTCHED ($K_t = 3.0$) 7050-T73651 PLATE (TRANSVERSE)

- X Rupture
- 1.0% creep
- △ 0.5% creep
- 0.2% creep

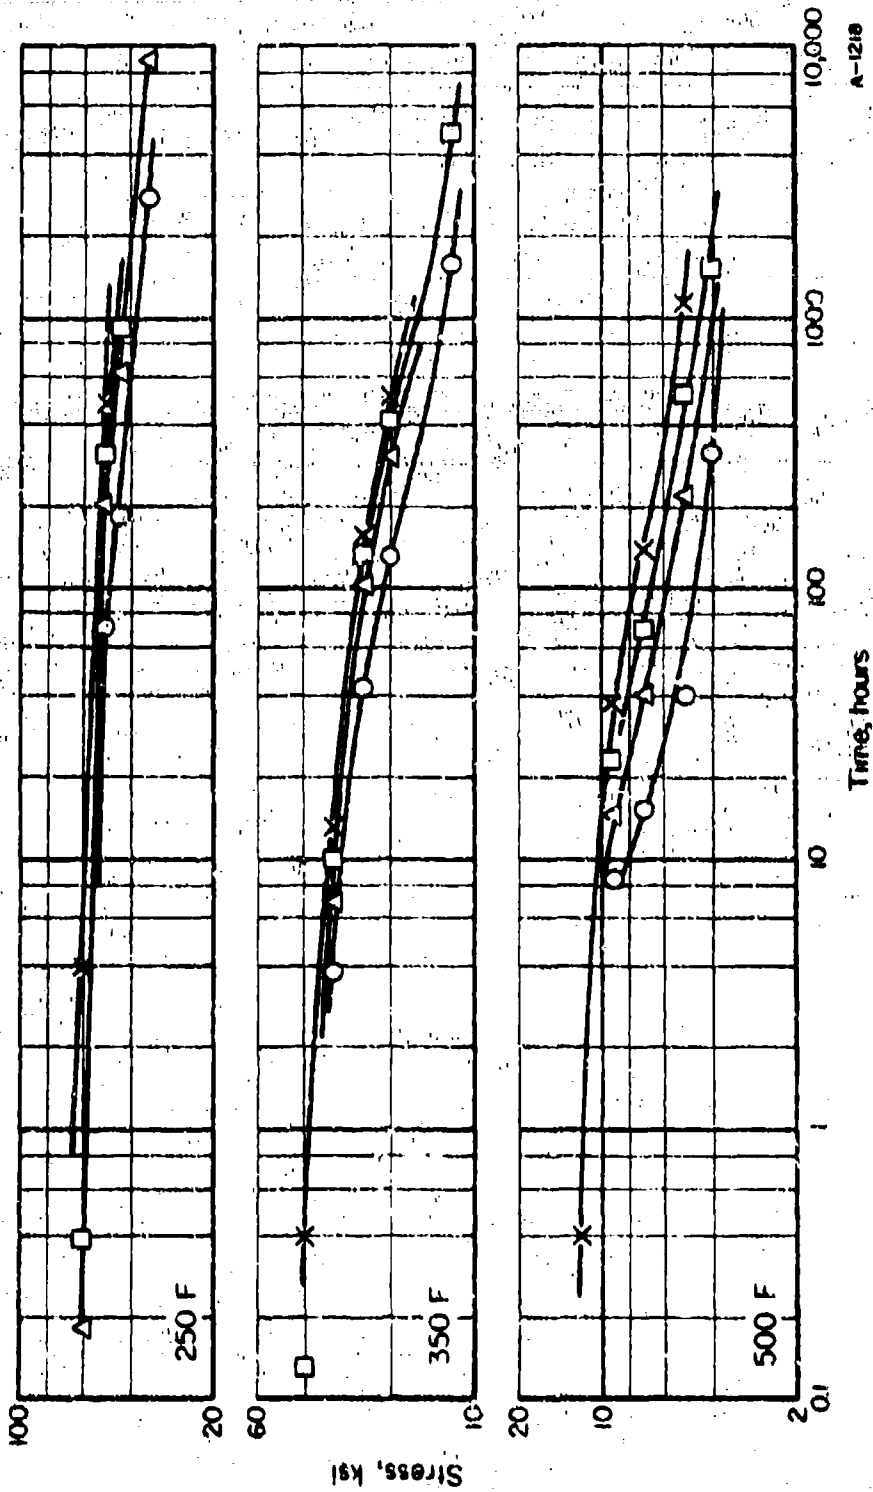


FIGURE 20. STRESS-RUPTURE AND PLASTIC DEFORMATION CURVES FOR 7050-T73651 PLATE (TRANSVERSE)

A-1218

21-6-9 Stainless Steel AlloyMaterial Description

Alloy 21-6-9 is a recent development of the Armco Steel Corporation. It is an austenitic stainless steel, combining high yield strength with good corrosion resistance. The room temperature yield strength of 21-6-9 is superior to Types 304, 321, and 347. It has good elevated temperature properties and retains high strength and toughness at subzero temperatures.

Armco 21-6-9 stainless steel is available in standard finishes in annealed or high tensile temper sheet and strip as well as in bar, wire, forging billets, and plate.

The materials used in this evaluation was an 0.072-inch thick sheet produced within the following composition limits

Carbon	0.08 max
Manganese	8.00 - 10.00
Phosphorus	0.060 max
Sulfur	0.030 max
Silicon	1.00 max
Chromium	19.00 - 21.50
Nickel	5.50 - 7.50
Nitrogen	0.15 - 0.40
Iron	Balance

Processing and Heat Treating

The specimen layout is shown in Figure 21. The alloy was evaluated in the as-received annealed condition.

Test Results

Tension. Results of tests on longitudinal and transverse specimens at room temperature, 400 F, 700 F, and 900 F are given in Table XVII. Typical stress-strain curves at temperature are presented in Figures 22 and 23. Effect-of-temperature curves are shown in Figure 26.

Compression. Test results for longitudinal and transverse specimens at room temperature, 400 F, 700 F, and 900 F are given in Table XVIII. Typical

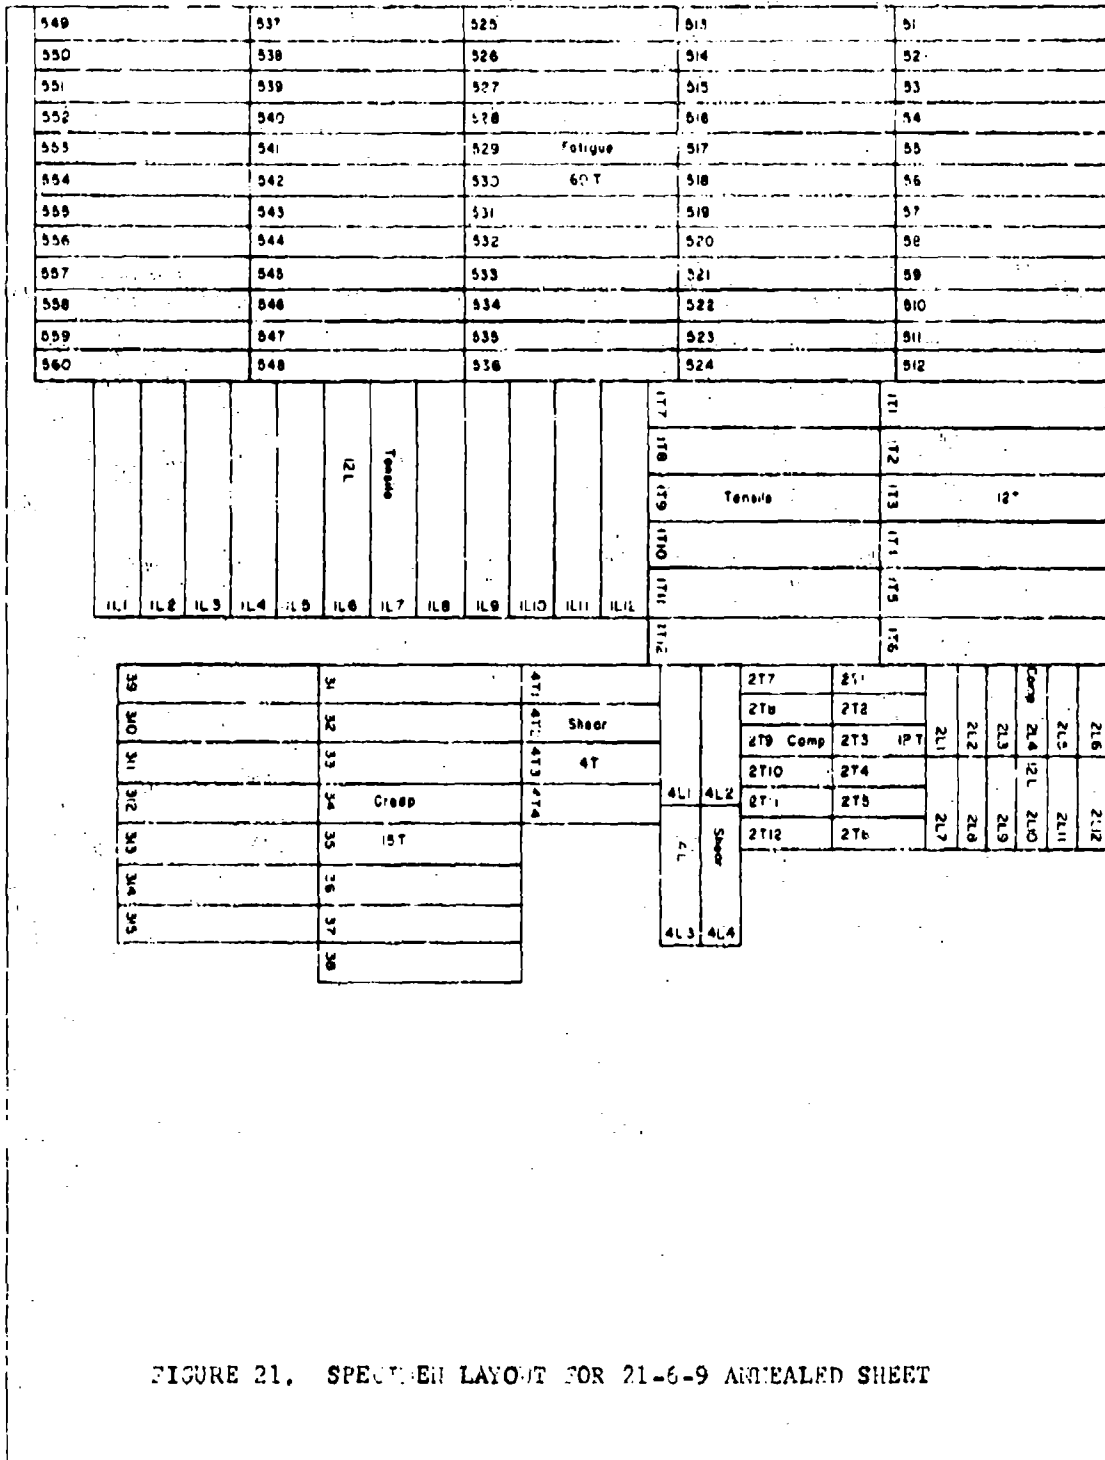


FIGURE 21. SPECIMEN LAYOUT FOR 21-6-9 ANNEALED SHEET

compressive stress-strain and tangent-modulus curves at temperature are presented in Figures 24 and 25. Effect-of-temperature curves are presented in Figure 17.

Shear. Results of sheet-shear type tests for longitudinal and transverse specimens at room temperature are given in Table XIX.

Bend. The minimum bend radius for this material was 1T.

Fracture Toughness. Tests were conducted on transverse (T-L) specimens of full-sheet thickness (0.072-inch) x 18 inches x 30 inches with an EDM flaw in the center. The net section yield stress at fracture was greater than the tensile yield strength of the material; therefore, the K values obtained are considered invalid.

Fatigue. Axial-load test results for transverse specimens at a stress ratio of $R = 0.1$ are given in Tables XX and XXI. These tests were performed on both unnotched and notched specimens at room temperature, 400 F, and 700 F. S-N curves are presented in Figures 28 and 29.

Creep and Stress Rupture. Tests were conducted for transverse specimens at 400 F, 700 F, and 900 F. Tabular test results are given in Table XXII. Log-stress versus log-time curves are presented in Figure 30.

Stress Corrosion. Tests were conducted as described in the experimental procedures section of this report. No cracks or fractures occurred in the 1000-hour test duration.

Thermal Expansion. The coefficient of expansion for this alloy is 10.6×10^{-6} in./in./F from 80 F to 1000 F.

Density. The density of this material is 0.283 lb./in.³.

TABLE XVII. TENSILE TEST RESULTS FOR ANNEALED
21-6-9 STAINLESS STEEL SHEET

Specimen Number	Ultimate Tensile Strength, ksi	0.2 Percent Offset Yield Strength, ksi	Elongation in 2 Inches, percent	Tensile Modulus, 10 ⁶ psi
<u>Longitudinal at Room Temperature</u>				
1L-1	113.0	64.3	54.0	26.7
1L-2	113.0	65.0	54.5	26.6
1L-3	113.0	65.1	56.5	26.4
Average	113.0	64.8	55.0	26.6
<u>Transverse at Room Temperature</u>				
1T-1	114.0	65.3	50.0	28.6
1T-2	113.0	66.3	50.0	28.2
1T-3	113.0	66.0	50.0	28.4
Average	113.3	65.7	50.0	28.4
<u>Longitudinal at 400 F</u>				
1L-4	88.4	42.3	44.0	21.2
1L-5	87.6	42.6	43.0	21.8
1L-6	98.4	42.6	43.5	20.2
Average	88.1	42.5	43.5	21.1
<u>Transverse at 400 F</u>				
1T-4	88.4	42.7	42.0	19.9
1T-5	88.4	42.5	42.0	20.5
1T-6	88.4	43.0	42.0	19.3
Average	88.4	42.7	42.0	19.9
<u>Longitudinal at 700 F</u>				
1L-7	84.2	35.9	46.0	24.8
1L-8	83.5	35.9	45.5	18.3
1L-9	83.5	35.9	45.5	22.0
Average	83.7	35.9	45.7	21.7
<u>Transverse at 700 F</u>				
1T-7	82.8	35.8	41.5	19.4
1T-8	83.4	35.9	42.0	18.4
1T-9	83.5	36.0	42.0	17.4
Average	83.2	35.9	41.8	18.4
<u>Longitudinal at 900 F</u>				
1L-10	76.0	33.0	43.0	20.4
1L-11	76.6	33.2	43.0	16.9
1L-12	75.7	32.9	43.0	20.2
Average	76.1	33.0	43.0	19.2
<u>Transverse at 900 F</u>				
1T-10	76.4	33.3	41.5	15.9
1T-11	76.6	33.3	41.0	17.6
1T-12	76.6	33.0	41.5	15.4
Average	76.5	33.2	41.3	16.3

TABLE XVIII. COMPRESSION TEST RESULTS FOR ANNEALED
21-6-9 STAINLESS STEEL SHEET

Specimen Number	0.2 Percent Offset Yield Strength, ksi	Compression Modulus, 10 ³ psi
<u>Longitudinal at Room Temperature</u>		
2L-1	67.2	29.3
2L-2	67.2	28.6
2L-3	67.2	27.8
Average	67.2	28.5
<u>Transverse at Room Temperature</u>		
2T-1	66.3	29.1
2T-2	66.5	29.0
2T-3	66.8	29.0
Average	66.5	29.0
<u>Longitudinal at 400 F</u>		
2L-4	44.4	26.2
2L-5	45.6	27.4
2L-6	45.4	26.6
Average	45.1	26.7
<u>Transverse at 400 F</u>		
2T-4	47.0	29.3
2T-5	46.7	29.0
2T-6	45.3	28.0
Average	46.3	28.8
<u>Longitudinal at 700 F</u>		
2L-7	40.2	25.8
2L-8	39.9	25.3
2L-9	41.4	26.4
Average	40.5	25.8
<u>Transverse at 700 F</u>		
2T-7	38.3	27.7
2T-8	37.2	25.5
2T-9	38.3	26.4
Average	37.9	26.5
<u>Longitudinal at 900 F</u>		
2L-10	35.5	25.8
2L-11	34.8	26.1
2L-12	33.8	24.1
Average	34.7	25.3
<u>Transverse at 900 F</u>		
2T-10	34.0	26.1
2T-11	34.1	25.8
2T-12	34.1	25.2
Average	34.1	25.7

TABLE XIX. SHEAR TEST RESULTS FOR ANNEALED
21-6-9 STAINLESS STEEL SHEET
AT ROOM TEMPERATURE

Specimen Number	Ultimate Shear Strength, ksi
<u>Longitudinal</u>	
4L-1	101.0
4L-2	102.0
4L-3	103.0
4L-4	103.0
Average	<u>102.3</u>
<u>Transverse</u>	
4T-1	102.0
4T-2	102.0
4T-3	104.0
4T-4	103.0
Average	<u>102.8</u>

TABLE XX. AXIAL LOAD FATIGUE TEST RESULTS FOR UNNOTCHED 21-6-9 ANNEALED STAINLESS STEEL SHEET (TRANSVERSE)

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-5	105.0	3,500
5-4	100.0	43,500
5-3	95.0	83,500
5-2	90.0	153,300
5-1	85.0	294,600
5-6	80.0	344,900
5-7	75.0	206,000
5-8	65.0	10,000,000 ^(a)
<u>400 F</u>		
5-9	100.0	(b)
5-14	90.0	200
5-10	90.0	500
5-16	87.5	122,700
5-13	85.0	63,600
5-17	82.5	153,300
5-12	80.0	110,500
5-18	77.5	258,400
5-15	75.0	10,167,000 ^(a)
<u>700 F</u>		
5-19	85.0	(b)
5-21	80.0	600
5-20	75.0	3,399,200
5-24	72.5	4,821,600
5-22	70.0	140,400
5-25	70.0	4,842,000
5-23	65.0	10,029,000 ^(a)

(a) Did not fail.

(b) Failed on first cycle.

TABLE XXI. AXIAL LOAD FATIGUE TEST RESULTS FOR NOTCHED ($K_t=3.0$)
21-6-9 ANNEALED STAINLESS STEEL SHEET (TRANSVERSE)

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-11	75.0	12,240
5-4	70.0	38,380
5-5	65.0	74,510
5-3	60.0	97,190
5-14	55.0	186,620
5-6	50.0	1,757,000
5-30	40.0	10,744,400 ^(a)
<u>400 F</u>		
5-13	75.0	10,300
5-31	70.0	11,200
5-22	65.0	14,000
5-21	55.0	26,900
5-20	45.0	84,400
5-32	40.0	204,600
5-17	35.0	10,589,500 ^(a)
<u>700 F</u>		
5-29	75.0	3,300
5-28	65.0	11,400
5-24	55.0	27,200
5-19	50.0	116,300
5-26	45.0	144,200
5-18	40.0	143,700
5-24	35.0	10,519,200 ^(a)

(a) Did not fail.

TABLE XXII. SUMMARY DATA ON CREEP AND RUPTURE PROPERTIES FOR 21-6-9 STAINLESS STEEL SHEET (TRANSVERSE)

Specimen Number	Stress, ksi	Temperature, F	Hours to Indicated Creep Deformation, percent						Initial Strain, percent	Rupture Time, hours	Elongation In 2 Inches, percent	Minimum Creep Rate, percent
			percent									
			0.1	0.2	0.5	1.0	2.0	2.0				
3-1	88	500	--	--	--	--	--	--	On Loading	41.3	--	
3-4	83	500	0.01	0.20	0.45	19	1,500 (a)	26.68	841.4 (b)	28.4	0.0005	
3-7	70	500	0.10	0.35	5.0	85	--	13.220	169.9 (b)	14.42	--	
3-9	40	500	5.0	70 (a)	1,455	4,800 (a)	--	0.826	650.1 (b)	1.355	0.0001	
3-12	35	500	--	3,000 (a)	--	--	--	0.229	715.1 (b)	0.251	--	
3-2	86	700	--	--	--	--	--	--	On Loading	43.1	--	
3-5	80	700	--	--	--	--	--	28.24	813.4 (b)	31.1	0.00007	
3-8	50	700	--	0.05	0.3	7.0	--	4.920	309.7 (b)	5.990	0.00002	
3-15	40	700	--	0.10	10 (a)	>1,000	--	1.452	498.6 (b)	2.050	--	
3-14	35	700	0.20	0.40	5,000 (a)	--	--	0.314	120.7 (b)	1.051	--	
3-11	30	700	--	10,000 (a)	--	--	--	0.180	268.5 (b)	0.218	--	
3-3	76.5	900	--	--	--	--	--	--	On Loading	42.2	--	
3-10	70	900	--	--	--	--	--	20.852	438.9	27.6	--	
3-6	65	900	--	--	--	--	--	10.8	753.7 ()	20.9	0.0006	
3-17	35	900	--	0.10	>1,000	--	--	1.260	480.0 ()	1.475	--	
3-16	30	900	--	5,000 (a)	--	--	--	0.198	738.5 ()	0.222	--	
3-13	25	900	--	--	--	--	--	0.162	289.4 ()	0.167	--	

(a) Estimate.

(b) Test discontinued.

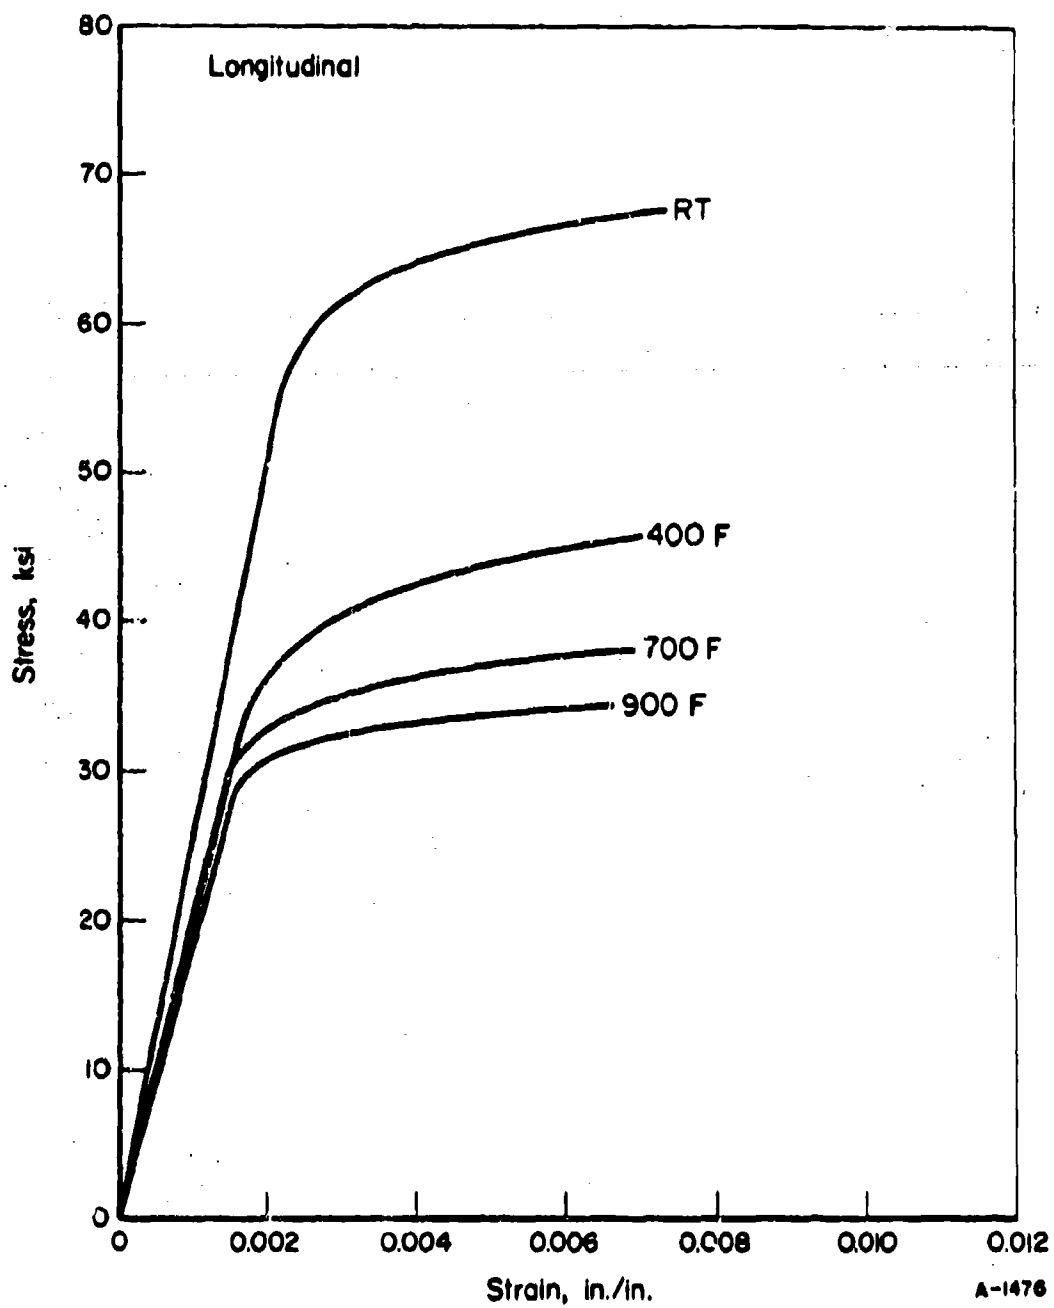


FIGURE 22. TYPICAL TENSILE STRESS-STRAIN CURVES AT TEMPERATURE FOR 21-6-9 ANNEALED SHEET (LONGITUDINAL)

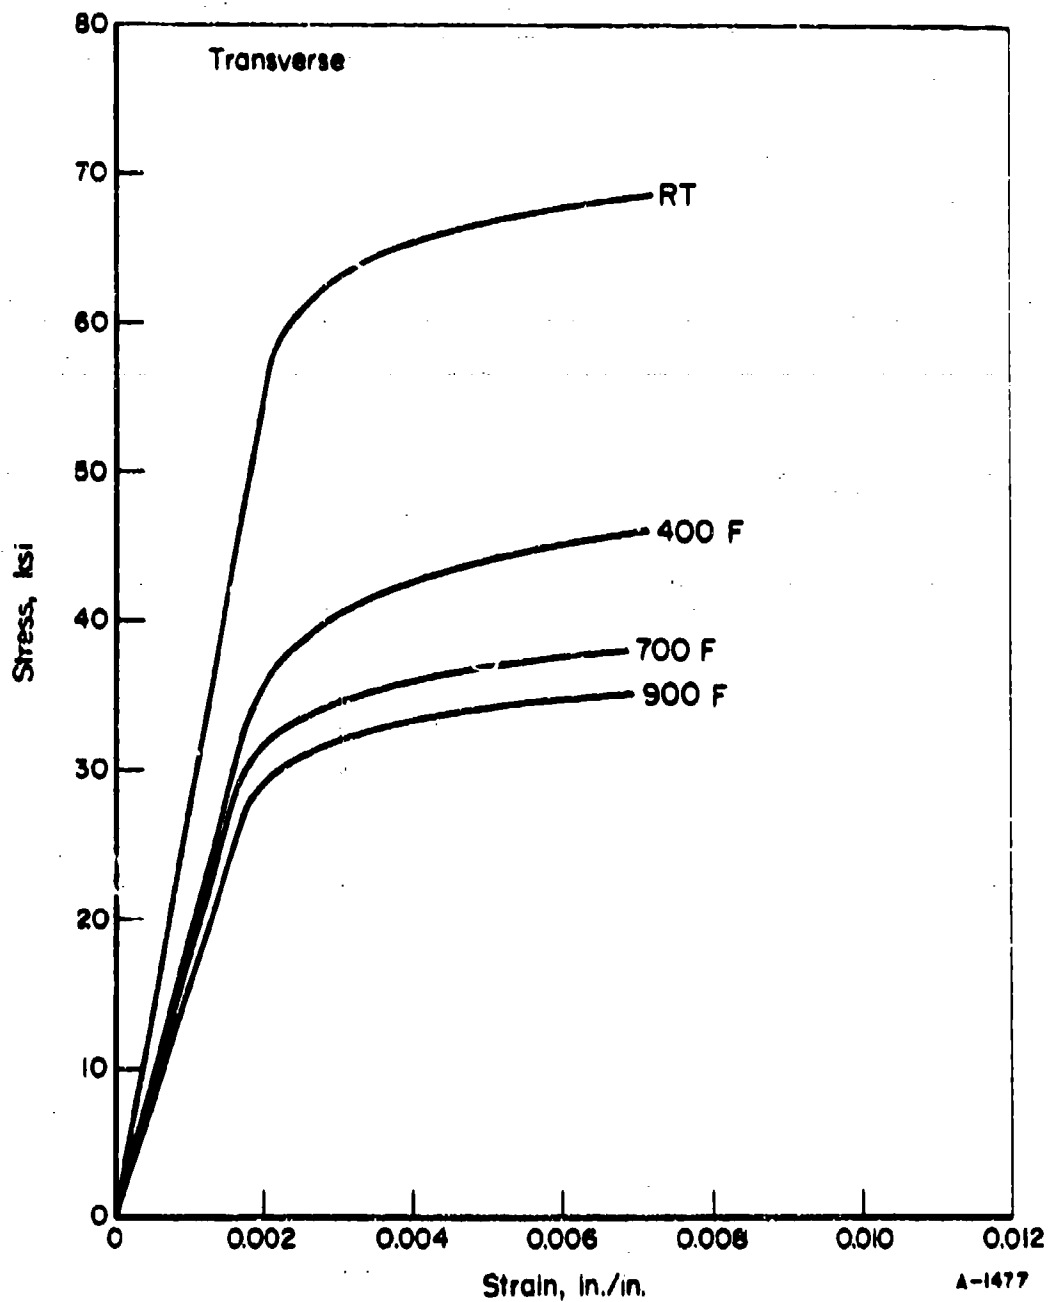


FIGURE 23. TYPICAL TENSILE STRESS-STRAIN CURVES AT TEMPERATURE FOR 21-6-9 ANNEALED SHEET (TRANSVERSE)

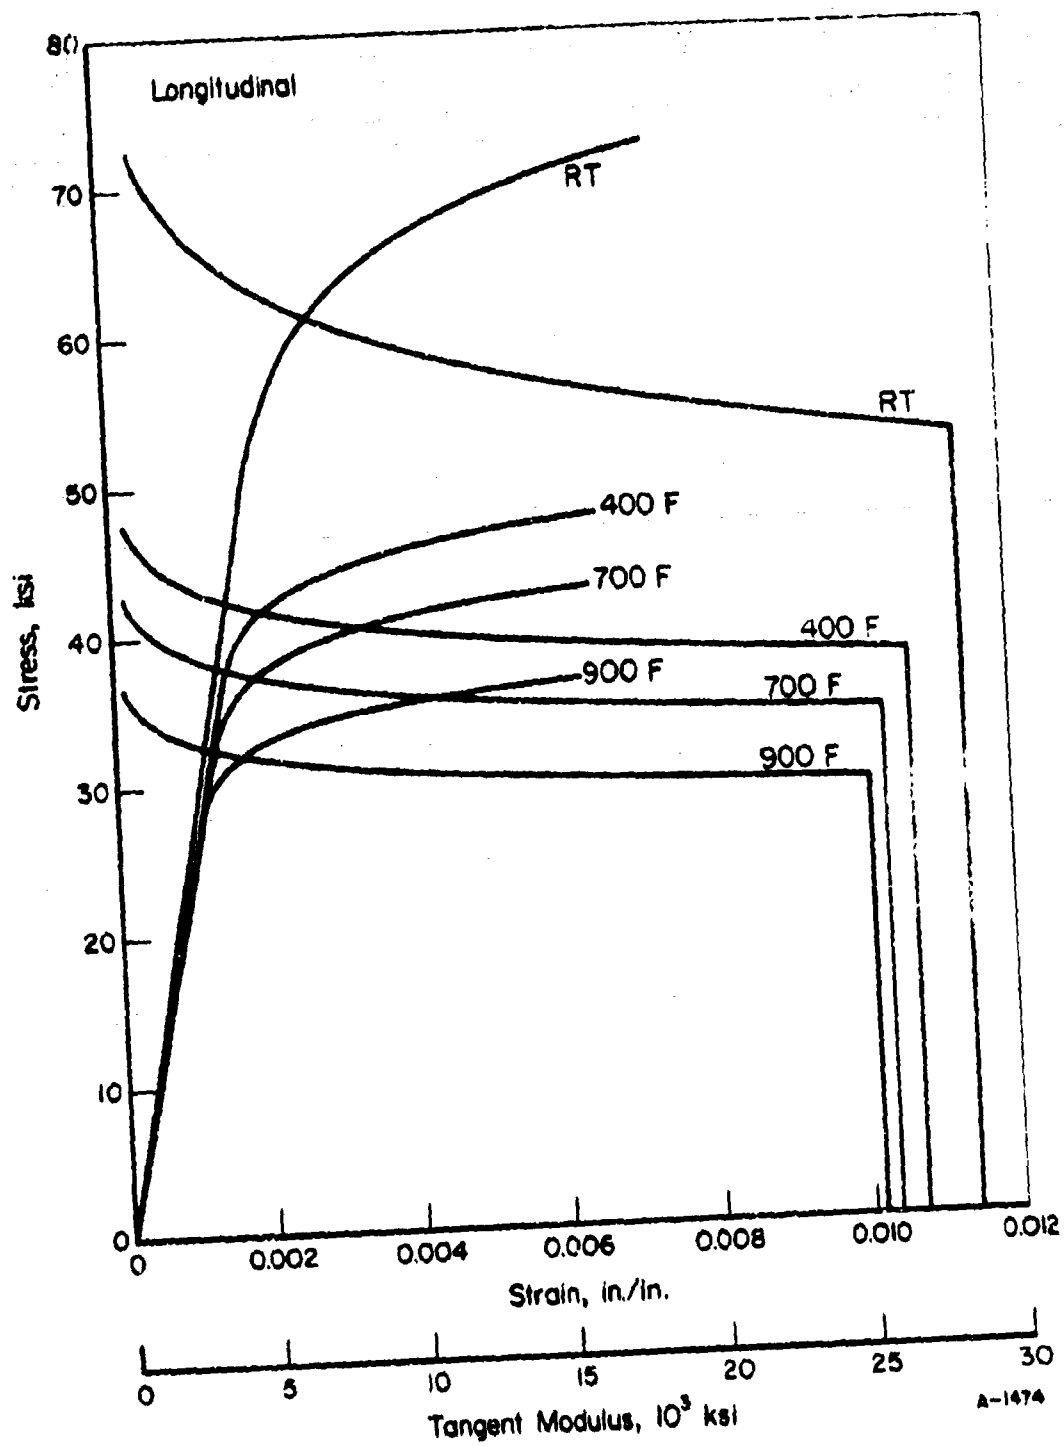


FIGURE 24. TYPICAL COMPRESSIVE STRESS-STRAIN AND TANGENT-MODULUS CURVES AT TEMPERATURE FOR 21-6-9 ANNEALED SHEET (LONGITUDINAL)

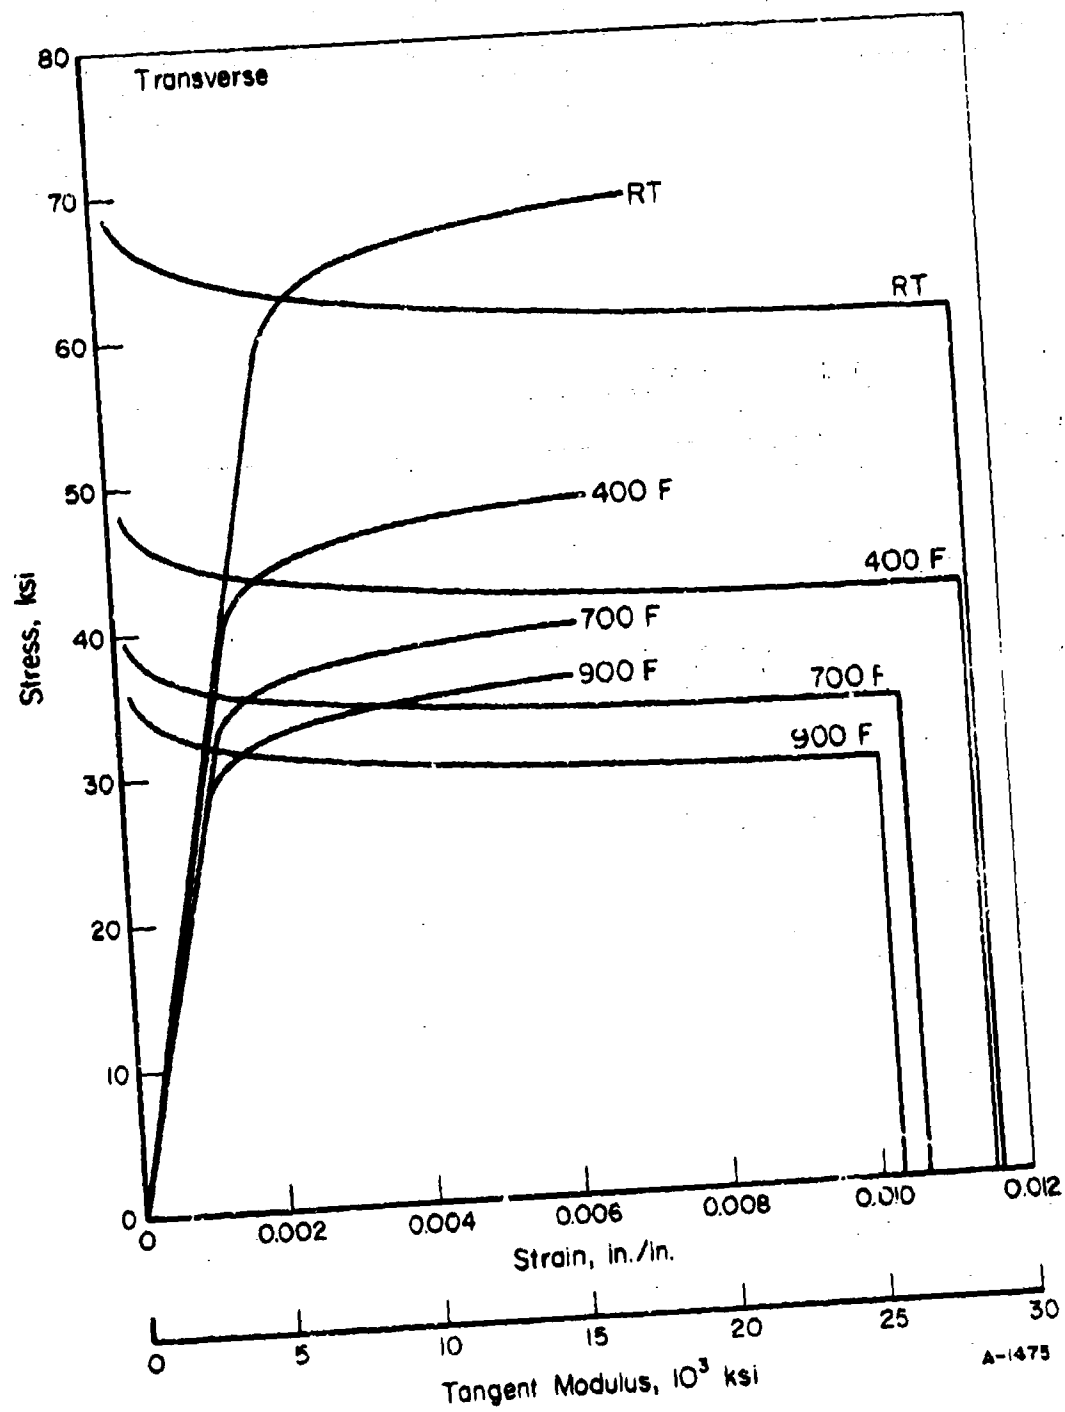


FIGURE 25. TYPICAL COMPRESSIVE STRESS-STRAIN AND TANGENT-MODULUS CURVES AT TEMPERATURE FOR 21-6-9 ANNEALED SHEET (TRANSVERSE)

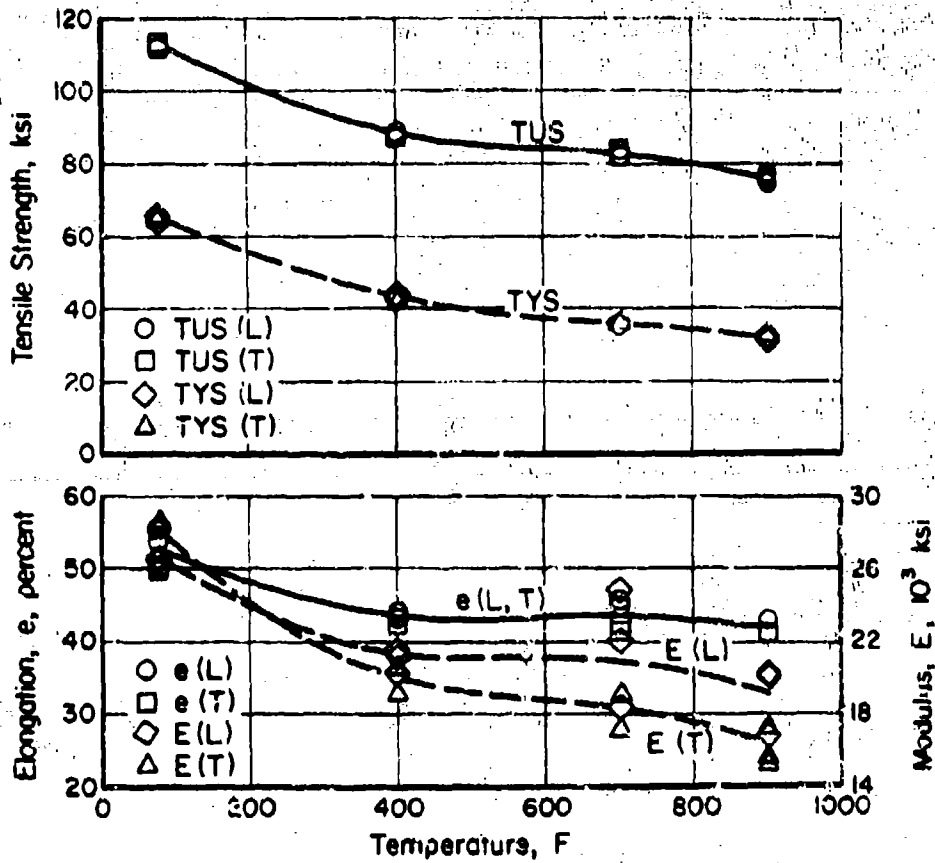


FIGURE 26. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF 21-6-9 ANNEALED SHEET.

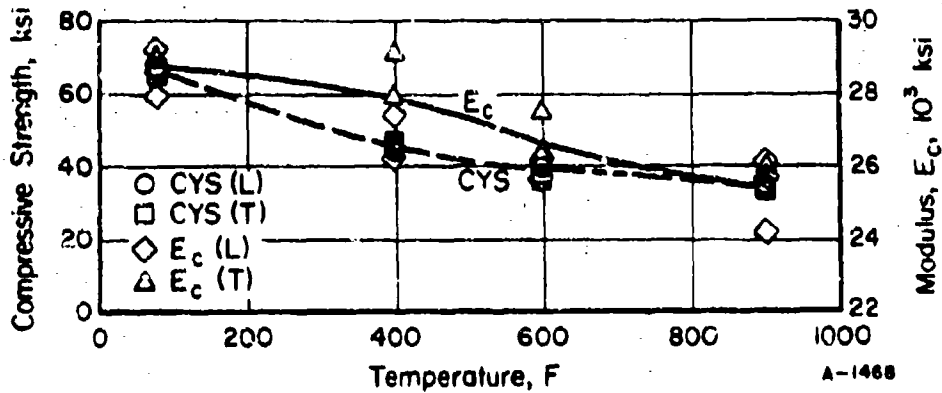


FIGURE 27. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF 21-6-9 ANNEALED SHEET

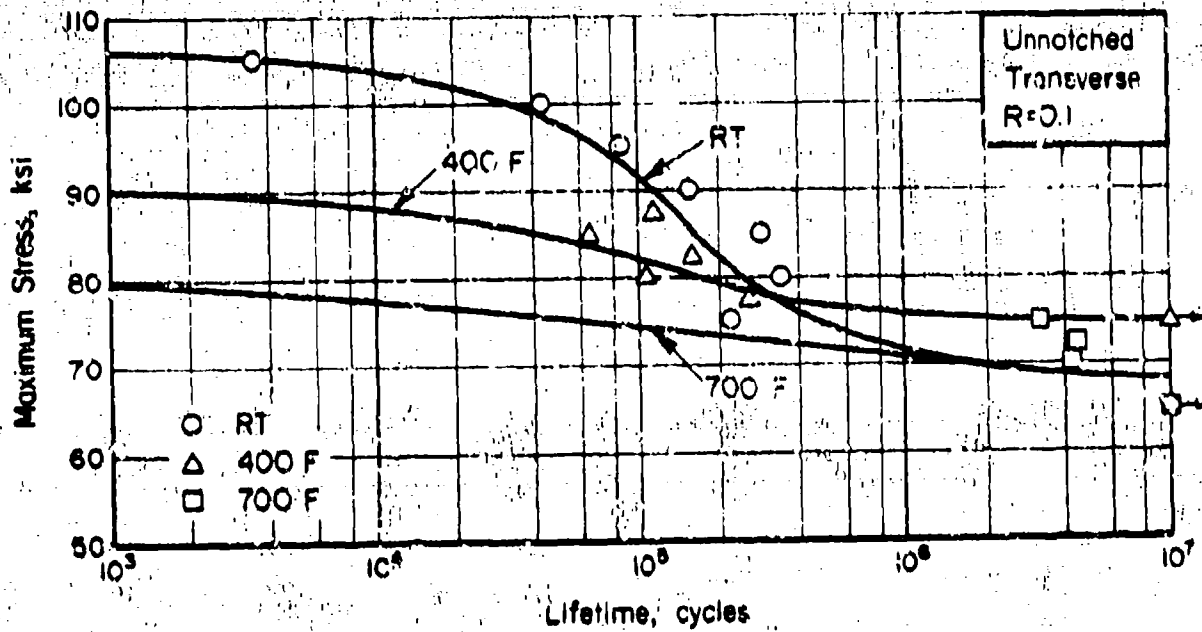


FIGURE 28. AXIAL LOAD FATIGUE BEHAVIOR OF UNNOTCHED 21-6-9 ANNEALED SHEET (TRANSVERSE)

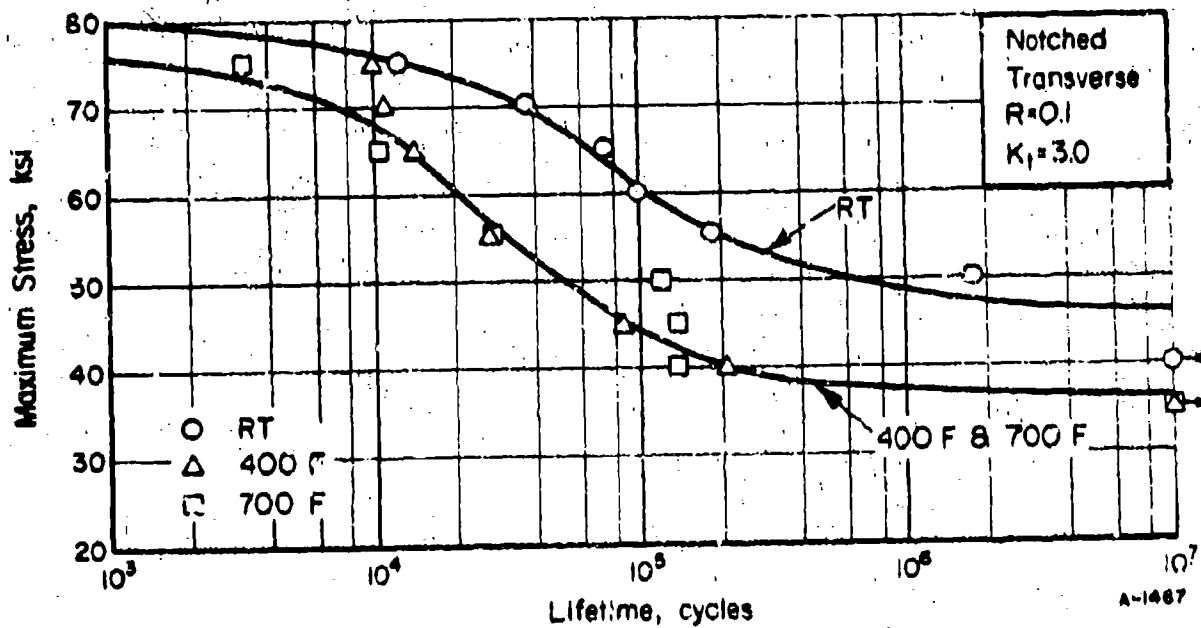


FIGURE 29. AXIAL LOAD FATIGUE BEHAVIOR OF NOTCHED ($K_t = 3.0$) 21-6-9 ANNEALED SHEET (TRANSVERSE)

- X Rupture
- 1.0% creep
- △ 0.5% creep
- 0.2% creep

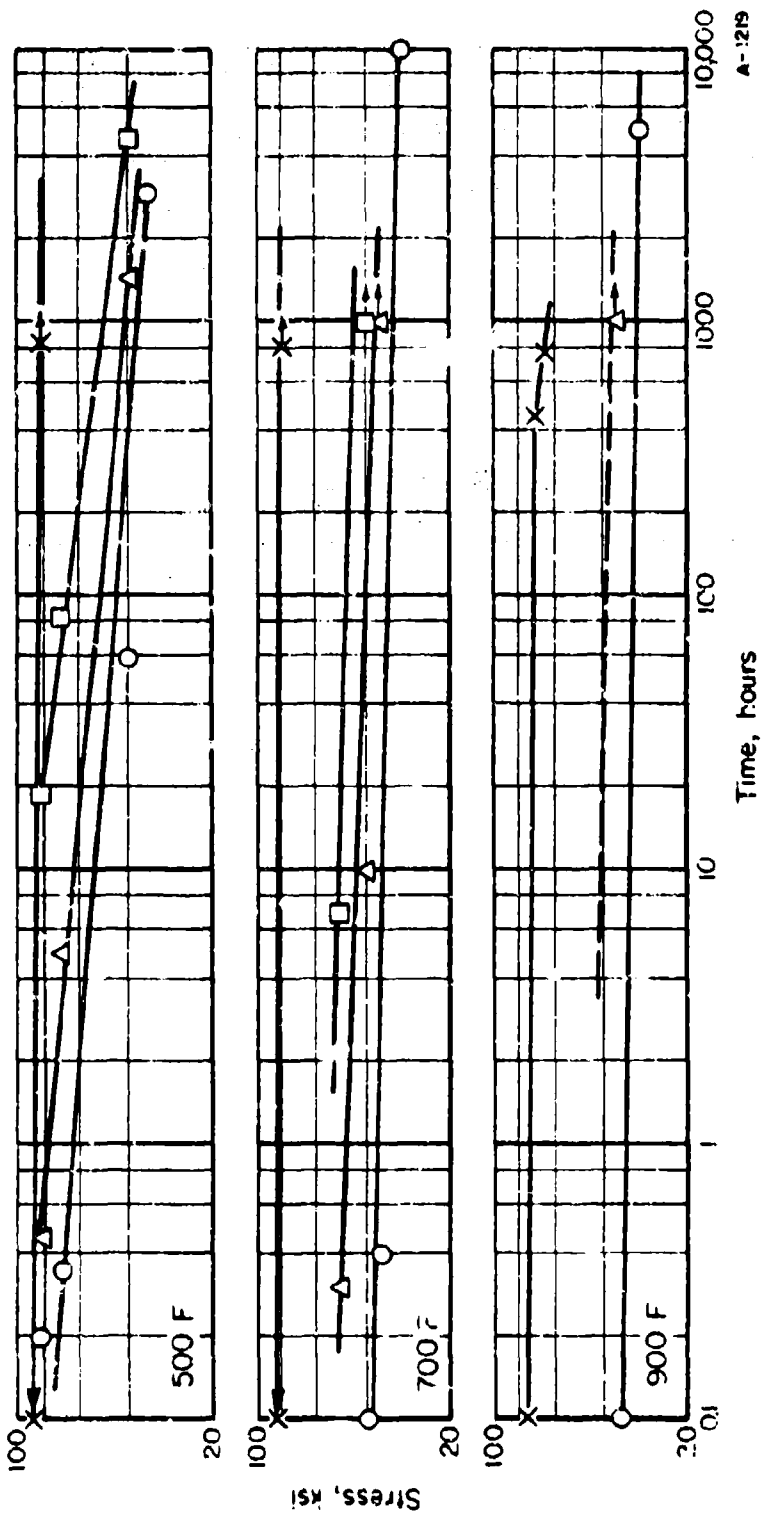


FIGURE 30. STRESS-RUPTURE AND PLASTIC DEFORMATION CURVES FOR 21-6-9 ANNEALED SHEET (TRANSVERSE)

Ti-8Mo-8V-2Fe-3Al AlloyMaterial Description

The 8Mo-8V-2Fe-3Al beta titanium alloy is a recent development of TIMET. The alloy was selected for full-scale evaluation after confirming (by TIMET) that it could be melted by the conventional consumable electrode vacuum arc process. It shows producibility and property characteristics that make it suitable for a variety of airframe applications. A variety of heat treatments are available to allow the designer to take advantage of its individual properties or its generally good overall properties.

The material used in this evaluation was an 0.040-inch-thick sheet from TIMET Heat K-5055 with the following composition

Molybdenum	8.0
Vanadium	8.2
Iron	2.0
Aluminum	3.0
Oxygen	0.14
Nitrogen	0.011
Titanium	Balance

Processing and Heat Treating

The specimen layout is shown in Figure 31. The material was received in the solution-treated condition. Specimens were aged at 900 F for 6 hours. This condition is called the high strength, fully-aged condition.

Test Results

Tension. Test results for longitudinal and transverse specimens at room temperature, 400 F, 600 F, and 800 F are given in Table XXIII. Stress-strain curves at temperature are presented in Figures 32 and 33. Effect-of-temperature curves are shown in Figure 36.

Compression. Test results for longitudinal and transverse specimens at room temperature, 400 F, 600 F, and 800 F are given in Table XXIV. Typical stress-strain and tangent modulus curves at temperature are presented in Figures 34 and 35. Effect-of-temperature curves are presented in Figure 37.

549	537	525	513	51																													
550	538	526	514	52																													
551	539	527	515	53																													
552	540	528	516	54																													
553	541	529 Fatigue	517	55																													
554	542	530 60 T	518	56																													
555	543	531	519	57																													
556	544	532	520	58																													
557	545	533	521	59																													
558	546	534	522	510																													
559	547	535	523	511																													
560	548	536	524	512																													
												177	178	179	180	171	172	173	174	175	176												
																Tensile				12T													
1L1	1L2	1L3	1L4	1L5	1L6	Tensile 12L		1L7	1L8	1L9	1L10	1L11	1L12																				
												4T1	4T2	4T3	4T4	4L1	4L2	Shear		2T7	2T1	2L6	2L2	2L7	2L2								
												Shear		4T		Shear		2T8		2T2	2L5	2L11											
																		2T9 Comp		2T3	12T	2L4 12L		2L9	2L9								
																		2T10		2T4	2L1		2L2	2L8	2L9								
																		2T11		2T5	4L		2L9		2L9								
																		2T12		2T6	4L3		4L4		4L4								
																						2L7		2L8		2L8							
39	310	311	312	313	314	315	31	32	33	34	Creep		35	36	37	38																	
																						15T											

FIGURE 31. SPEC. LAYOUT FOR T1-8Mo-8V-2Fe-3Al SHEET

Shear. Test results for longitudinal and transverse specimens at room temperature are given in Table XXV.

Fracture Toughness. Specimens were full-sheet thickness (0.040-inch) by 18 inches wide by 36 inches long with an EDM flaw in the center. The average K_{Ic} obtained from four transverse (T-L) specimens was 50 ksi $\sqrt{\text{in.}}$. By existing ASTM criteria, this is considered a valid K_{Ic} value.

Fatigue. Axial load tests were conducted on transverse specimens, both unnotched and notched, at a stress ratio of $R = 0.1$. Test temperatures were room temperature, 400 F, and 600 F. Tabular test results are given in Tables XXVI and XXVII. S-N curves are presented in Figures 38 and 39.

Creep and Stress-Rupture. Tests were performed at 550 F, 700 F, and 900 F. Tabular test results are given in Table XXVIII. Log-stress versus log-time curves are presented in Figure 40.

Stress-Corrosion. Tests were performed as described in the experimental procedures section of this report. No failures or cracks occurred in the 1000-hour test duration.

Thermal Expansion. The coefficient of thermal expansion for this alloy is 5.0×10^{-6} in./in./F from 68 F to 800 F.

Density. The density of this alloy is 0.175 lb./in.³.

TABLE XXIII. TENSILE TEST RESULTS FOR SOLUTION-TREATED AND AGED Ti-8Mo-8V-2Fe-3Al ALLOY SHEET

Specimen Number	Ultimate Tensile Strength, ksi	0.2 Percent Offset Yield Strength, ksi	Elongation in 2 Inches, percent	Tensile Modulus, 10 ³ psi
<u>Longitudinal at Room Temperature</u>				
1L-1	160.0	143.0	12.0	13.6
1L-2	162.0	147.0	12.0	13.6
1L-3	159.0	144.0	11.0	13.7
Average	<u>160.3</u>	<u>144.7</u>	<u>11.7</u>	<u>13.6</u>
<u>Transverse at Room Temperature</u>				
1T-1	176.0	160.0	9.0	15.4
1T-2	175.0	157.0	10.0	14.9
1T-3	173.0	157.0	9.5	14.5
Average	<u>174.7</u>	<u>158.0</u>	<u>9.5</u>	<u>14.9</u>
<u>Longitudinal at 400 F</u>				
1L-4	148.0	123.0	9.5	13.2
1L-5	149.0	124.0	9.0	13.5
1L-6	149.0	123.0	8.5	13.2
Average	<u>148.7</u>	<u>123.3</u>	<u>9.0</u>	<u>12.9</u>
<u>Transverse at 400 F</u>				
1T-4	153.0	135.0	7.0	14.4
1T-5	158.0	133.0	6.5	13.8
1T-6	155.0	132.0	7.0	14.1
Average	<u>155.3</u>	<u>133.3</u>	<u>6.8</u>	<u>14.1</u>
<u>Longitudinal at 600 F</u>				
1L-7	144.0	116.0	7.5	12.3
1L-8	147.0	118.0	7.5	12.4
1L-9	147.0	119.0	7.0	12.5
Average	<u>146.3</u>	<u>117.7</u>	<u>7.3</u>	<u>12.4</u>
<u>Transverse at 600 F</u>				
1T-7	152.0	123.0	6.5	13.2
1T-8	153.0	124.0	6.5	13.5
1T-9	152.0	125.0	7.0	13.0
Average	<u>152.3</u>	<u>124.0</u>	<u>6.7</u>	<u>13.2</u>
<u>Longitudinal at 800 F</u>				
1L-10	139.0	102.0	21.0	12.1
1L-11	140.0	110.0	19.0	11.8
1L-12	134.0	105.0	16.0	11.4
Average	<u>137.7</u>	<u>105.7</u>	<u>18.7</u>	<u>11.8</u>
<u>Transverse at 800 F</u>				
1T-10	139.0	112.0	16.5	12.3
1T-11	146.0	118.0	16.0	12.4
1T-12	138.0	108.0	16.0	12.2
Average	<u>141.0</u>	<u>112.7</u>	<u>16.2</u>	<u>12.3</u>

TABLE XXIV. COMPRESSION TEST RESULTS FOR SOLUTION TREATED AND AGED Ti-8Mo-8V-2Fe-3Al ALLOY SHEET

Specimen Number	0.2 Percent Offset Yield Strength, ksi	Compression Modulus, 10 ⁶ psi
<u>Longitudinal at Room Temperature</u>		
2L-1	177.0	15.9
2L-2	177.0	15.8
2L-3	179.0	16.0
Average	<u>177.7</u>	<u>15.9</u>
<u>Transverse at Room Temperature</u>		
2T-1	190.0	16.8
2T-2	192.0	16.8
2T-3	193.0	17.1
Average	<u>191.7</u>	<u>16.9</u>
<u>Longitudinal at 400 F</u>		
2L-4	138.0	14.4
2L-5	164.0	15.9
2L-6	142.0	14.7
Average	<u>140.7</u>	<u>14.5</u>
<u>Transverse at 400 F</u>		
2T-4	164.0	16.1
2T-5	164.0	15.9
2T-6	163.0	16.2
Average	<u>163.7</u>	<u>16.1</u>
<u>Longitudinal at 600 F</u>		
2L-7	141.0	14.5
2L-8	137.0	13.9
2L-9	138.0	14.1
Average	<u>138.7</u>	<u>14.2</u>
<u>Transverse at 600 F</u>		
2T-7	152.0	14.9
2T-8	154.0	14.9
2T-9	149.0	14.7
Average	<u>151.7</u>	<u>14.8</u>
<u>Longitudinal at 800 F</u>		
2L-10	134.0	12.7
2L-11	136.0	12.5
2L-12	134.0	12.9
Average	<u>134.7</u>	<u>12.7</u>
<u>Transverse at 800 F</u>		
2T-10	140.0	13.5
2T-11	139.0	13.7
2T-12	137.0	13.5
Average	<u>138.7</u>	<u>13.6</u>

TABLE XXV. SHEAR TEST RESULTS FOR SOLUTION-TREATED AND AGED Ti-8Mo-8V-2Fe-3Al ALLOY SHEET AT ROOM TEMPERATURE

Specimen Number	Ultimate Shear Strength, ksi
<u>Longitudinal</u>	
4L-1	92.9
4L-2	102.0
4L-3	102.0
4L-4	<u>100.5</u>
Average	<u>100.5</u>
<u>Transverse</u>	
4T-1	103.0
4T-2	106.0
4T-3	109.0
4T-4	<u>109.0</u>
Average	<u>106.8</u>

TABLE XXVI. AXIAL LOAD FATIGUE TEST RESULTS FOR UN-NOTCHED, SOLUTION-TREATED AND AGED Ti-8Mo-8V-2Fe-3Al ALLOY SHEET (TRANSVERSE)

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-2	110.0	8,200
5-1	100.0	16,800
5-3	90.0	24,000
5-4	80.0	34,800
5-5	70.0	61,400 ^(a)
5-25	70.0	324,000 ^(b)
5-6	65.0	11,153,000 ^(b)
5-7	60.0	11,053,400 ^(b)
<u>400 F</u>		
5-11	110.0	12,100
5-12	100.0	13,500
5-13	90.0	22,400
5-15	85.0	40,600
5-14	80.0	33,900
5-16	75.0	36,500 ^(c)
5-9	70.0	290,000 ^(b)
5-10	70.0	10,940,500 ^(b)
5-8	60.0	10,245,100 ^(b)
<u>700 F</u>		
5-17	110.0	4,010
5-18	100.0	4,870
5-19	90.0	7,650
5-20	80.0	12,500
5-21	70.0	100,380 ^(b)
5-22	60.0	10,352,900 ^(b)

(a) Failed in grip.

(b) Did not fail.

(c) Failed at thermocouple.

TABLE XXVII. AXIAL LOAD FATIGUE TEST RESULTS FOR NOTCHED
(K_t = 3.0) SOLUTION-TREATED AND AGED Ti-8Mo-
8V-2Fe-3Al ALLOY SHEET (TRANSVERSE)

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-31	80.0	3,700
5-32	70.0	4,300
5-35	60.0	6,600
5-33	50.0	12,500
5-36	40.0	17,000
5-34	30.0	911,500 ^(a)
5-37	20.0	10,001,300 ^(a)
<u>400 F</u>		
5-39	80.0	4,700
5-40	70.0	5,500
5-41	60.0	6,700
5-42	50.0	11,400
5-43	40.0	21,100
5-44	30.0	10,329,900 ^(a)
5-38	20.0	10,001,700 ^(a)
<u>700 F</u>		
5-45	80.0	2,900
5-46	70.0	3,200
5-47	60.0	5,100
5-48	50.0	8,200
5-49	40.0	26,500
5-50	30.0	73,400 ^(a)
5-51	25.0	16,537,900 ^(a)

(a) Did not fail.

TABLE XXVIII. SUMMARY DATA ON CREEP AND RUPTURE PROPERTIES FOR Ti-8Mo-8V-2Fe-3Al ALLOY SHEET (TRANSVERSE)

Specimen Number	Stress, ksi	Temperature, F	Hours to Indicated Creep Deformation, percent					Initial Strain, percent	Rupture Time, hours	Elongation in 2 Inches, percent	Minimum Creep Rate, percent
			0.1	0.2	0.5	1.0	2.0				
3-1	156	700	--	--	--	--	--	Or. Loading	5.3	--	
2-2	150	700	--	--	--	--	--	0.1	3.6	--	
3-3	140	700	0.05	0.20	1.3	4.2	13	62.3	12.0	0.047	
3-8	100	700	1.6	4	11	23	75	989.7 (b)	7.1	0.0025	
3-10	60	700	4	8	27	95	500 (a)	14.6 (b)	1.578	--	
3-11	30	700	20	55	450 (a)	2000 (a)	--	313.3 (b)	0.529	0.00036	
3-4	75	900	--	0.1	0.3	0.65	1.7	8.1	31.1	1.2	
3-5	50	900	0.05	0.15	0.6	2.0	6.7	59.4	50.2	0.22	
3-7	25	900	0.50	2.5	10	40	155	1406.2 (b)	57.3	0.008	
3-13	12	900	4.3	20	153	450 (a)	--	172.8 (b)	0.647	0.0018	
3-6	155	550	--	--	--	--	--	On Loading	8.9	--	
3-9	145	550	0.3	2.8	30	105 (a)	1200 (a)	1104.6 (b)	4.50	0.0003	
3-12	110	550	8.0	26	98	3500 (a)	--	173.9 (b)	1.682	--	
3-16	70	550	30	103	360 (a)	--	--	234.6 (b)	0.780	--	

(a) Estimate.

(b) Test discontinued.

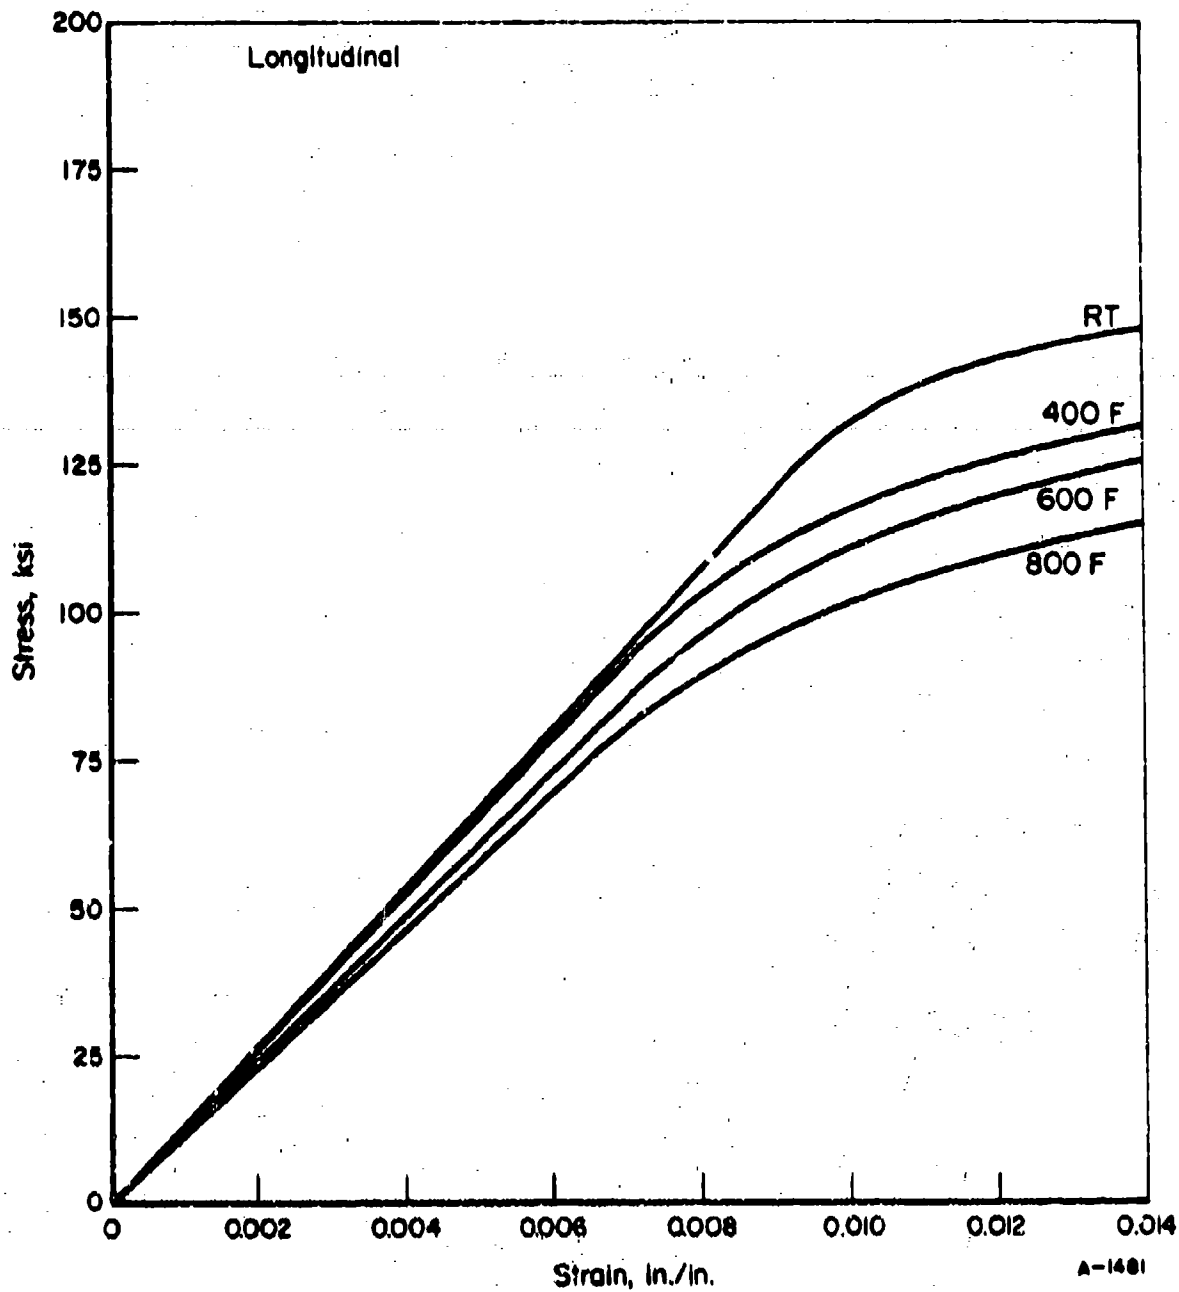


FIGURE 32. TYPICAL TENSILE STRESS-STRAIN CURVES AT TEMPERATURE FOR SOLUTION-TREATED AND AGED Ti-8Mo-8V-2Fe-3Al SHEET (LONGITUDINAL)

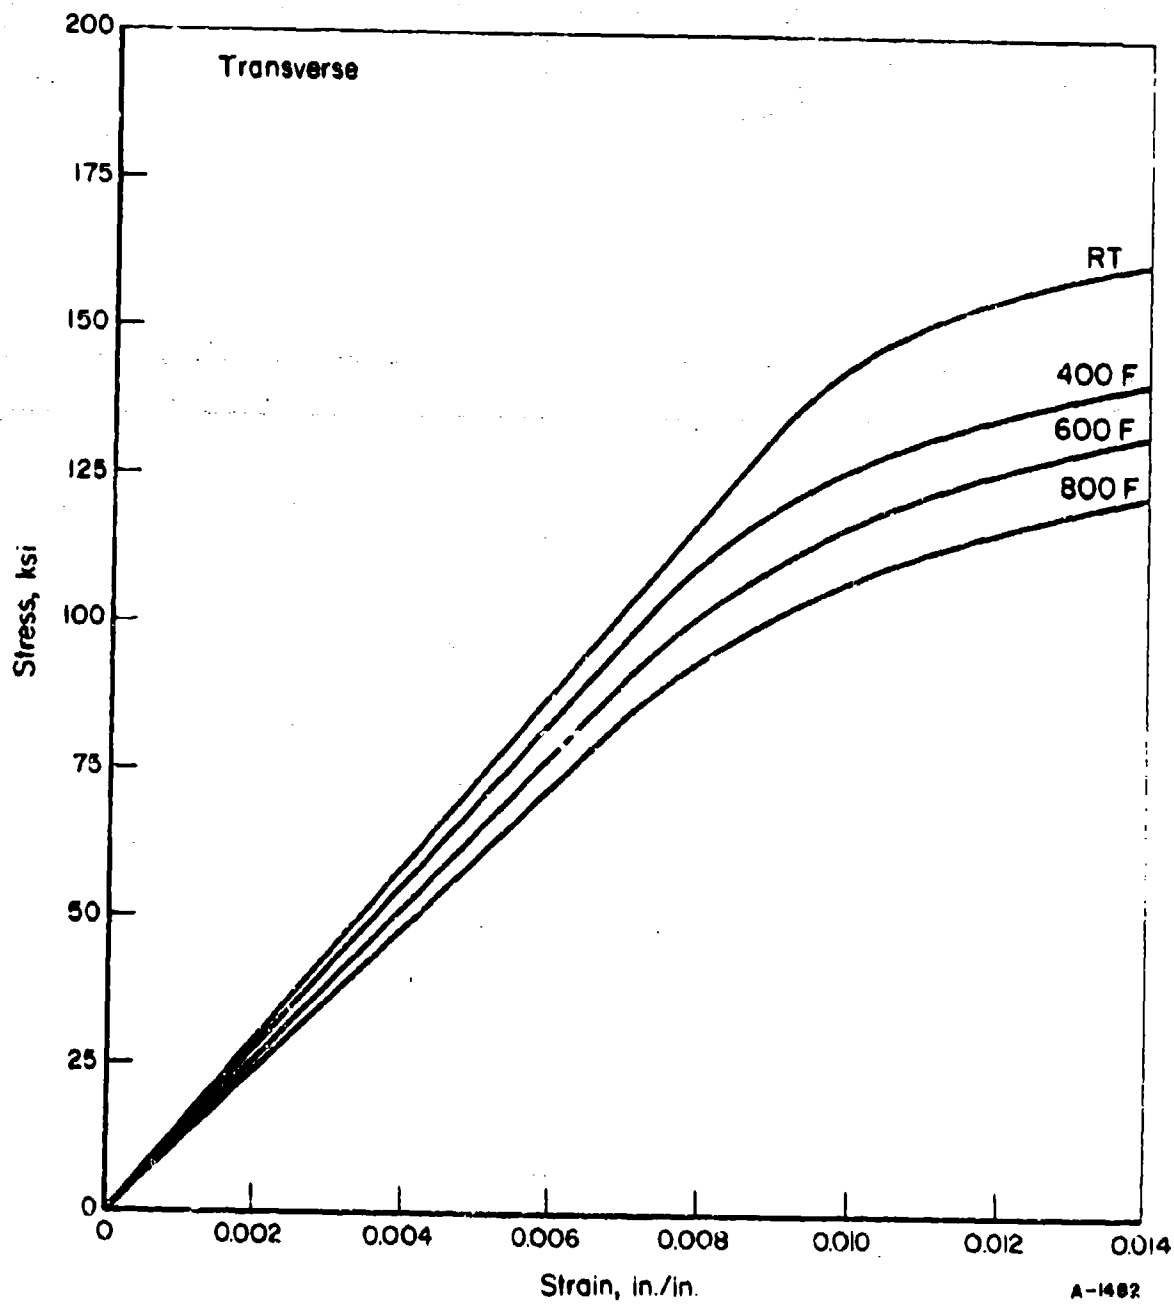


FIGURE 33. TYPICAL TENSILE STRESS-STRAIN CURVES AT TEMPERATURE FOR SOLUTION-TREATED AND AGED Ti-8Nb-8V-2Fe-3Al SHEET (TRANSVERSE)

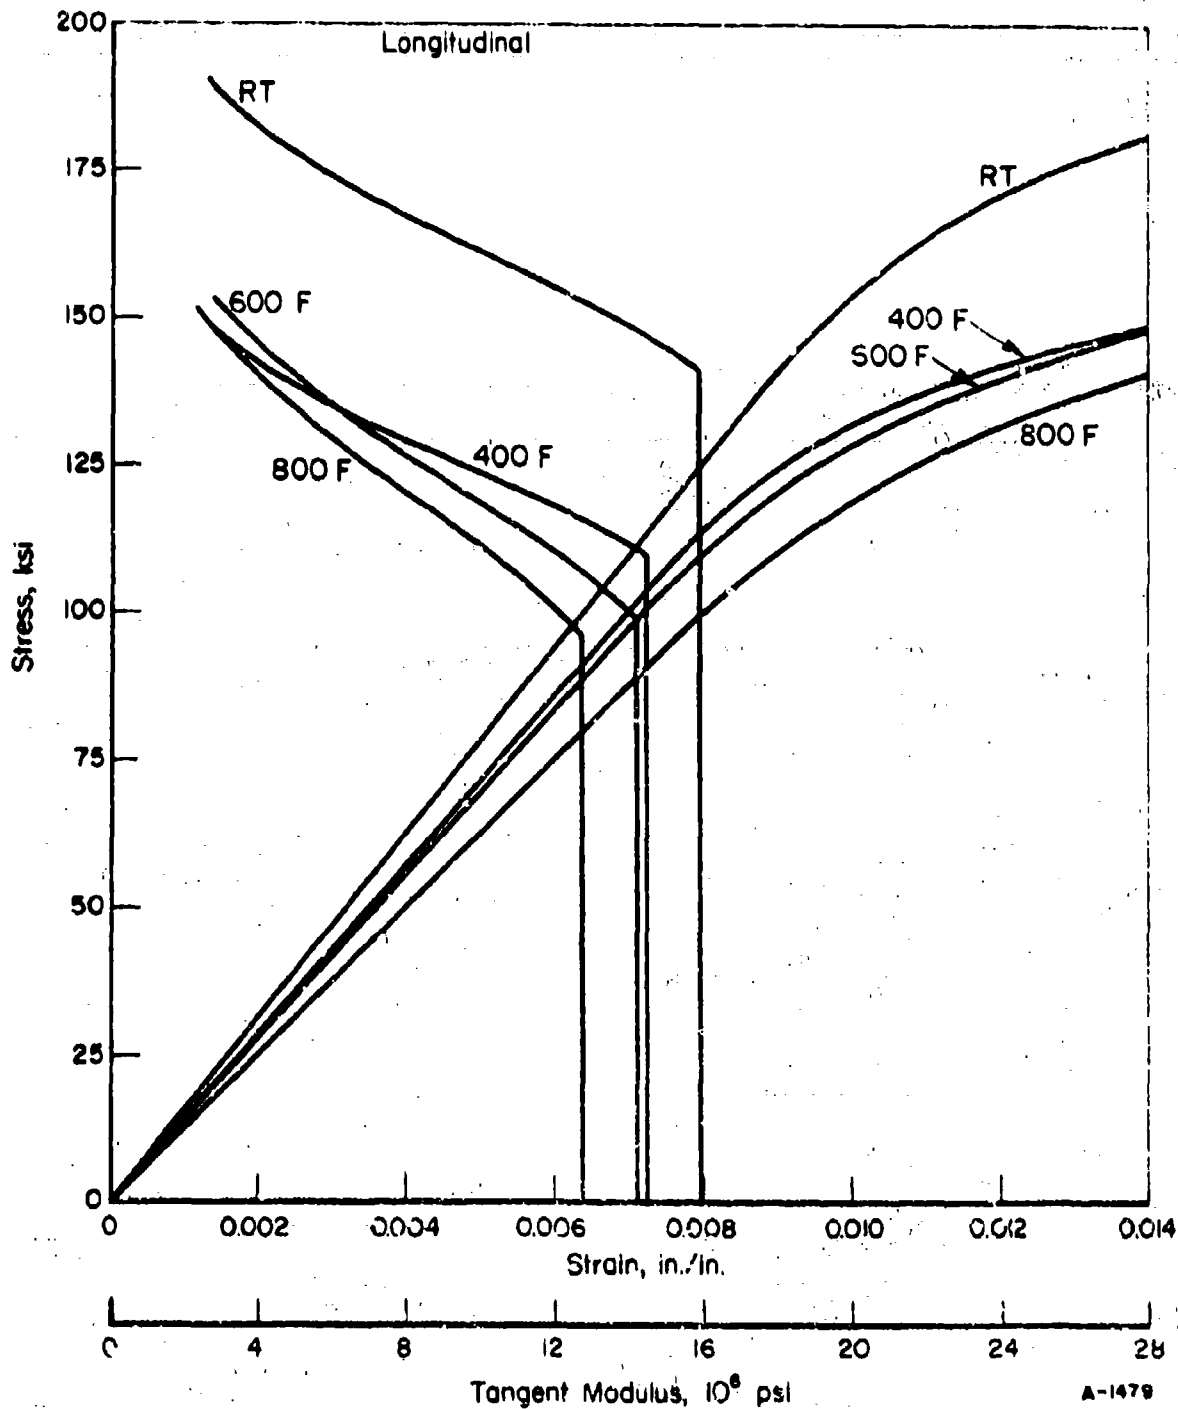


FIGURE 34. TYPICAL COMPRESSIVE STRESS-STRAIN AND TANGENT-MODULUS CURVES AT TEMPERATURE FOR SOLUTION-TREATED AND AGED T1-8Mo-8V-2Fe-3Al SHEET (LONGITUDINAL)

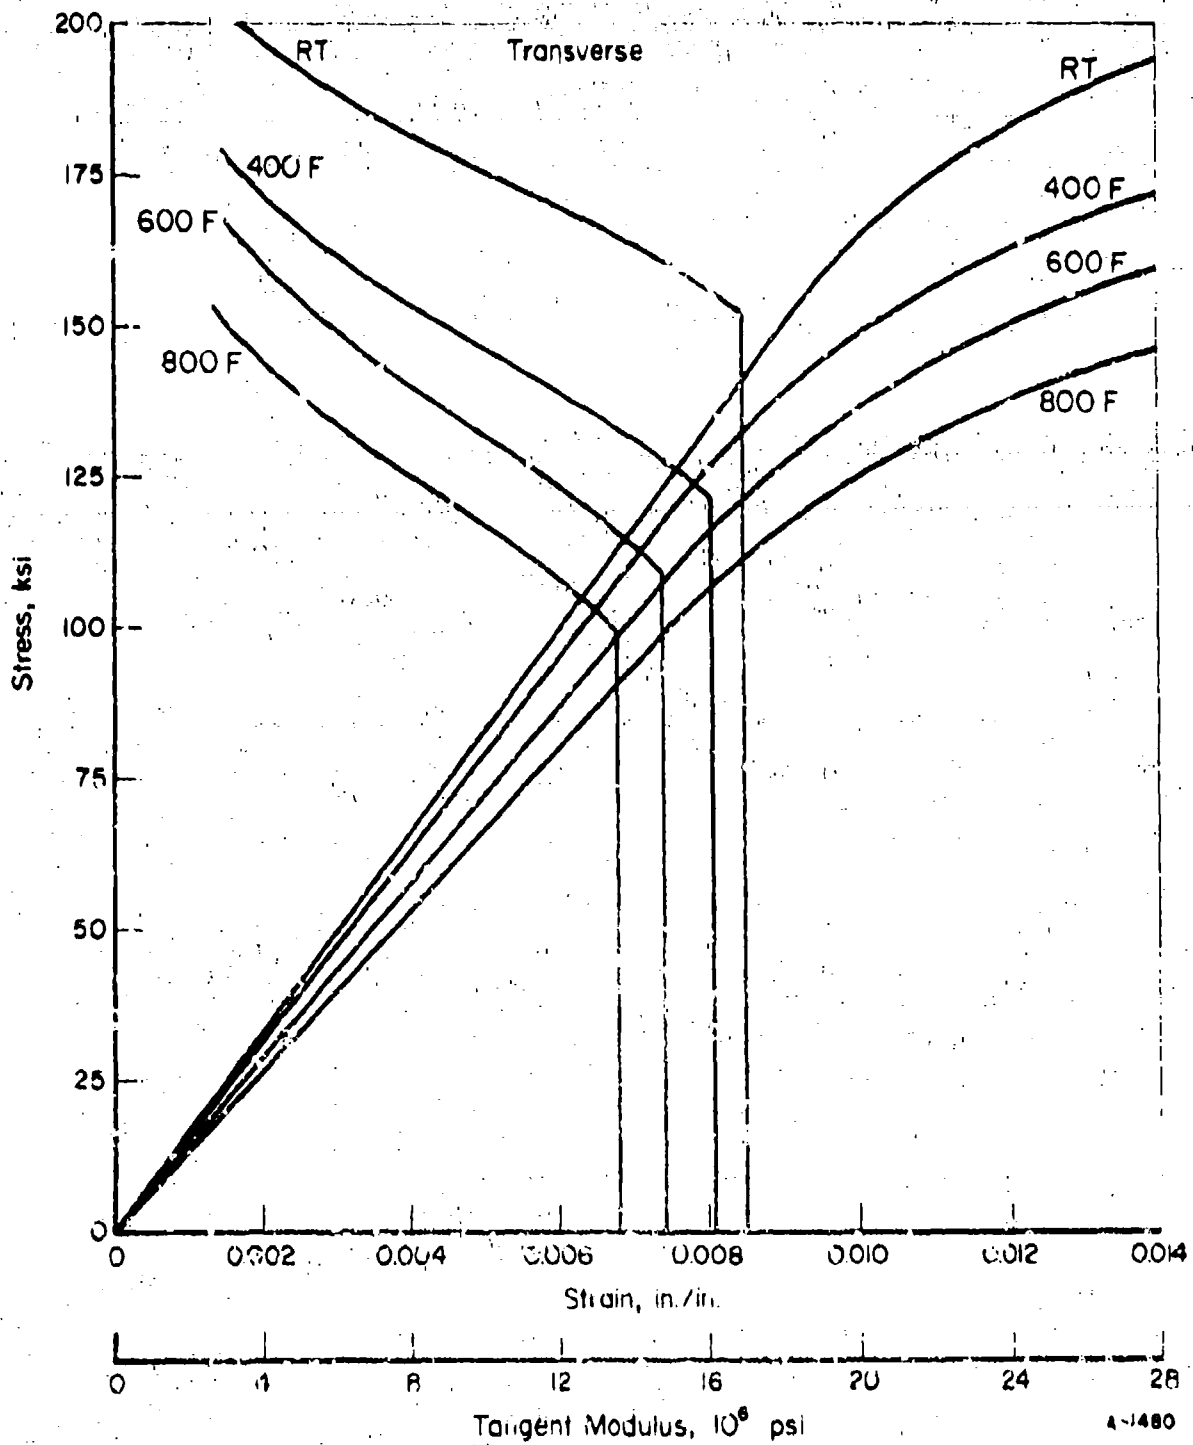


FIGURE 35. TYPICAL COMPRESSIVE STRESS-STRAIN AND TANGENT-MODULUS CURVES AT TEMPERATURE FOR SOLUTION-TREATED AND AGED TI-6AL-4V-2FE-0.1AL SHEET (TRANSVERSE)

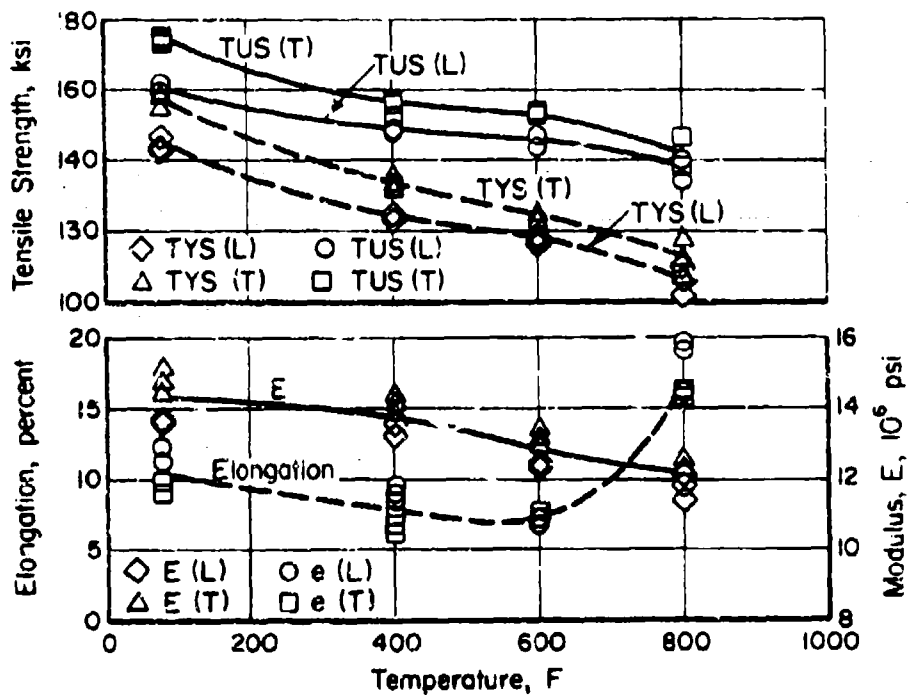


FIGURE 36. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF SOLUTION-TREATED AND AGED Ti-8Mo-8V-2Fe-3Al SHEET

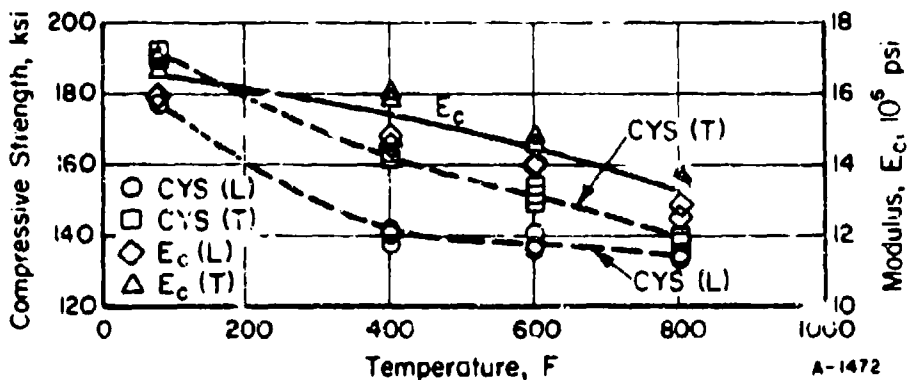


FIGURE 37. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF SOLUTION-TREATED AND AGED Ti-8Mo-8V-2Fe-3Al SHEET

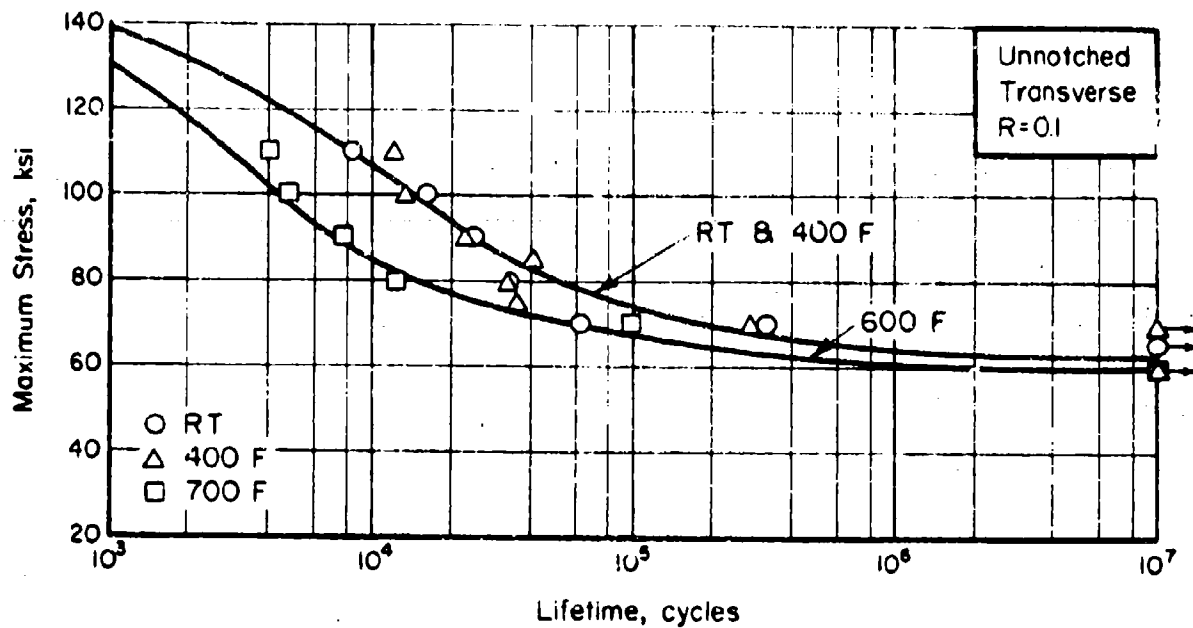


FIGURE 38. AXIAL LOAD FATIGUE BEHAVIOR OF UNNOTCHED SOLUTION-TREATED AND AGED T1-8Mo-8V-2Fe-3Al SHEET (TRANSVERSE)


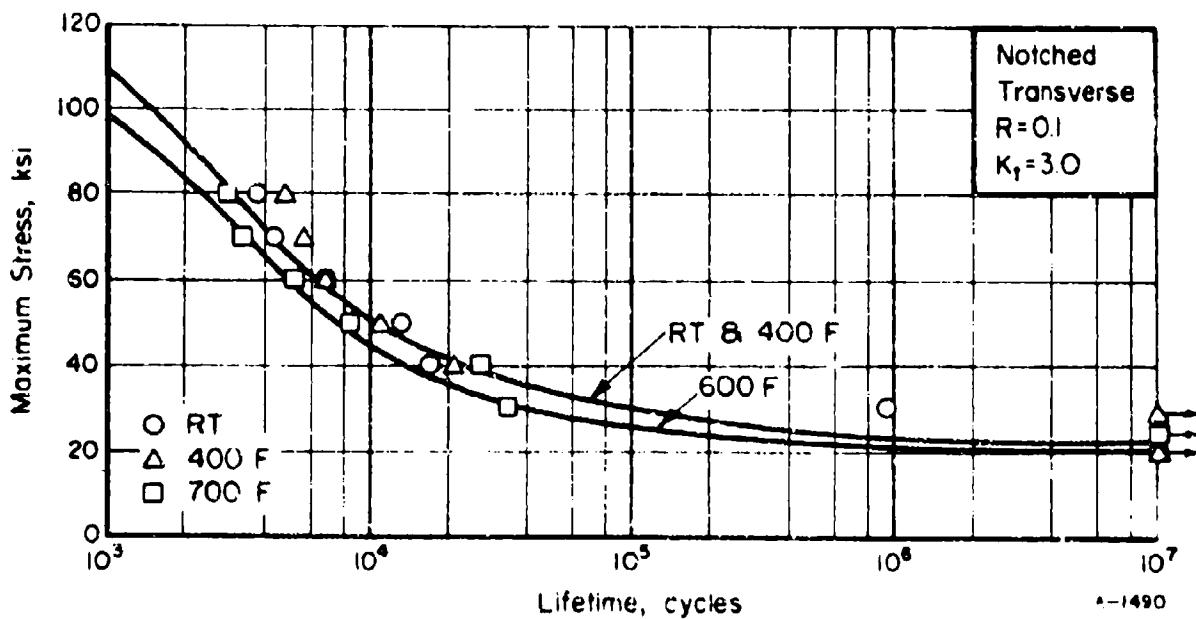


FIGURE 39. AXIAL LOAD FATIGUE BEHAVIOR OF NOTCHED ($K_t = 3.0$) SOLUTION-TREATED AND AGED T1-8Mo-8V-2Fe-3Al SHEET (TRANSVERSE)

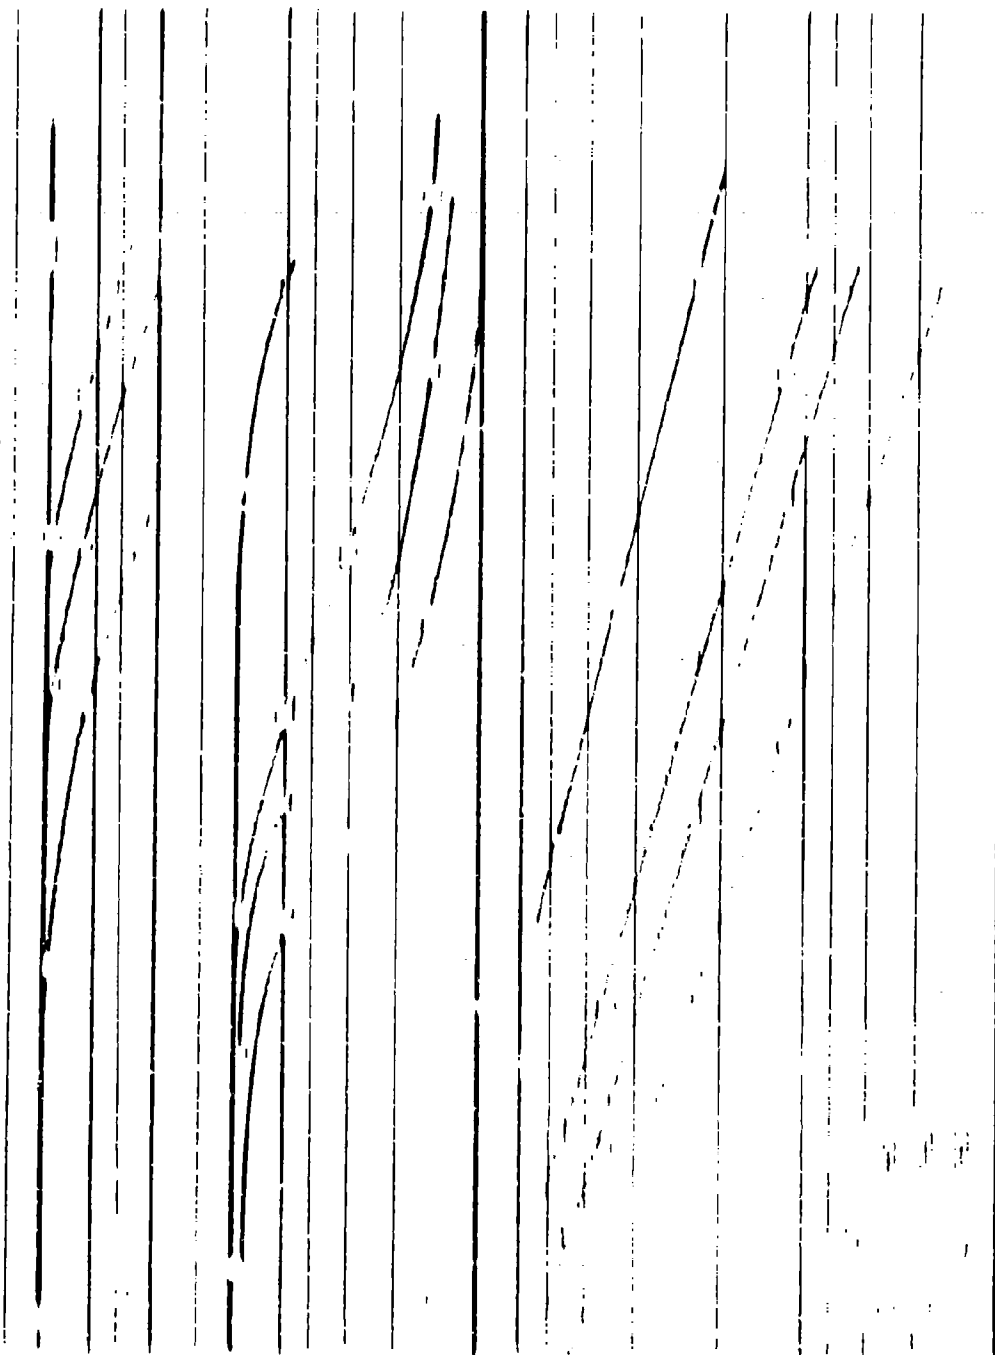

Ti-6Al-2Zr-2Sn-2Mo-2Cr Alloy

Material Description

This alloy is a recent development of RMI Company. It is an alpha-beta type alloy designed for deep hardenability. Preliminary information shows the material to have low density, high modulus, high toughness, and good producibility. Strength retention to 800 F is good.

The material used for this evaluation was a 1 1/2-inch-thick plate from RMI ingot number 890180.

Processing and Heat Treating

The specimen layout is shown in Figure 41. The material was received in the solution-treated (1740 F, 1 hour, AC) condition and specimens were aged at 1000 F for 8 hours.

Test Results

Tension. Results of tests in both the longitudinal and transverse directions at room temperature, 400 F, 600 F, and 800 F are given in Table XXIX. Typical stress-strain curves at temperature are shown in Figures 42 and 43. Effect-of-temperature curves are presented in Figure 46.

Compression. Results of tests in both the longitudinal and transverse directions at room temperature, 400 F, 600 F, and 800 F are given in Table XXX. Typical stress-strain and tangent-modulus curves at temperature are shown in Figures 44 and 45. Effect-of-temperature curves are shown in Figure 47.

Shear. Results of pin shear tests at room temperature for longitudinal and transverse specimens are given in Table XXXI.

Impact. Results of Charpy V-notch tests at room temperature in both the longitudinal and transverse directions are given in Table XXXII.

Fracture Toughness. Results of slow-bend type tests in both the longitudinal (L-T) and transverse (T-L) directions are given in Table XXXIII. Even though the candidate K_Q values do not meet the rigorous $a, T, < 2.5 \left(\frac{K_Q}{TYS}\right)^2$ criteria they are above $2.2 \left(\frac{K_Q}{TYS}\right)^2$ and should be considered good indicative K_{Ic} values.




FIGURE 41. SPECIMEN LAYOUT FOR Ti-6Al-2Zr-2Sn-2Mo-2Cr PLATE

Fatigue. Axial load fatigue tests were conducted at room temperature, 400 F, and 600 F for unnotched and notched transverse specimens at a stress ratio of $R = 0.1$. Results are given in tabular form in Tables XXXIV and XXXV. S-N curves are presented in Figures 48 and 49.

Creep and Stress Rupture. Tests were conducted on transverse specimens at 400 F, 600 F, and 800 F. Tabular test results are given in Table XXXVI. Log-stress versus log-time curves are presented in Figure 50.

Stress Corrosion. Specimens were tested as described in the experimental procedures section of this report. No fractures or cracks occurred in the 1000-hour test duration.

Thermal Expansion. The thermal expansion coefficient for this alloy is 5.1×10^{-6} in./in./F for 70 to 800 F.

Density. The density value is 0.162 lb./in.³.

TABLE XXIX. TENSILE TEST RESULTS FOR SOLUTION-TREATED AND
AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr ALLOY PLATE

Specimen Number	Ultimate Tensile Strength, ksi	0.2 Percent Offset Yield Strength, ksi	Elongation in 1-inch, percent	Reduction in Area, percent	Tensile Modulus, 10 ⁶ psi
<u>Longitudinal at Room Temperature</u>					
1L-1	169.0	155.0	18.0	25.0	17.9
1L-2	168.0	156.0	18.0	24.8	17.9
1L-3	<u>168.0</u>	<u>156.0</u>	<u>18.0</u>	<u>24.6</u>	<u>17.8</u>
Average	168.3	155.6	18.0	24.8	17.9
<u>Transverse at Room Temperature</u>					
1T-1	168.0	157.0	18.0	24.0	17.5
1T-2	169.0	156.0	17.5	27.3	17.7
1T-3	<u>169.0</u>	<u>157.0</u>	<u>17.5</u>	<u>27.4</u>	<u>18.3</u>
Average	168.7	156.6	17.7	26.2	17.8
<u>Longitudinal at 400 F</u>					
1L-4	144.0	111.0	17.5	29.8	15.4
1L-5	147.0	120.0	20.5	34.6	17.0
1L-6	<u>145.0</u>	<u>117.0</u>	<u>20.5</u>	<u>35.3</u>	<u>15.2</u>
Average	145.3	116.0	19.5	33.2	15.9
<u>Transverse at 400 F</u>					
1T-4	145.0	120.0	19.0	34.5	15.9
1T-5	147.0	120.0	20.0	33.5	16.1
1T-6	<u>146.0</u>	<u>119.0</u>	<u>20.0</u>	<u>33.0</u>	<u>16.7</u>
Average	146.0	119.7	19.7	33.7	16.2
<u>Longitudinal at 600 F</u>					
1L-7	138.0	107.0	18.5	34.5	14.8
1L-8	139.0	107.0	20.0	36.0	16.2
1L-9	<u>140.0</u>	<u>107.0</u>	<u>17.0</u>	<u>34.2</u>	<u>15.8</u>
Average	139.0	107.0	18.5	34.9	15.6
<u>Transverse at 600 F</u>					
1T-7	139.0	108.0	18.5	30.4	16.0
1T-8	140.0	109.0	18.0	35.0	16.0
1T-9	<u>140.0</u>	<u>109.0</u>	<u>18.0</u>	<u>34.6</u>	<u>16.0</u>
Average	139.7	108.7	18.2	33.3	16.0
<u>Longitudinal at 800 F</u>					
1L-10	131.0	99.5	22.0	41.3	13.8
1L-11	132.0	102.0	22.0	44.0	14.5
1L-12	<u>133.0</u>	<u>102.0</u>	<u>20.0</u>	<u>40.9</u>	<u>14.9</u>
Average	132.0	101.2	21.3	42.1	14.4
<u>Transverse at 800 F</u>					
1T-10	133.0	106.0	21.0	44.7	13.9
1T-11	131.0	102.0	21.0	37.4	14.4
1T-12	<u>132.0</u>	<u>104.0</u>	<u>21.0</u>	<u>42.0</u>	<u>15.5</u>
Average	132.0	104.0	21.0	41.4	14.6

TABLE XXX. COMPRESSION TEST RESULTS FOR SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr ALLOY PLATE

Specimen Number	0.2 Percent Offset Yield Strength, ksi	Compressive Modulus, 10 ⁶ psi
<u>Longitudinal at Room Temperature</u>		
2L-1	168.0	17.8
2L-2	170.0	18.5
2L-3	<u>171.0</u>	<u>18.0</u>
Average	169.7	18.1
<u>Transverse at Room Temperature</u>		
2T-1	172.0	18.3
2T-2	174.0	18.5
2T-3	<u>174.0</u>	<u>18.6</u>
Average	173.3	18.5
<u>Longitudinal at 400 F</u>		
2L-4	132.0	16.5
2L-5	125.0	17.2
2L-6	<u>128.0</u>	<u>16.5</u>
Average	128.3	16.7
<u>Transverse at 400 F</u>		
2T-4	130.0	16.3
2T-5	130.0	16.5
2T-6	<u>128.0</u>	<u>16.2</u>
Average	129.3	16.3
<u>Longitudinal at 600 F</u>		
2L-7	113.0	15.7
2L-8	113.0	16.4
2L-9	<u>111.0</u>	<u>15.4</u>
Average	112.3	15.8
<u>Transverse at 600 F</u>		
2T-7	114.0	15.9
2T-8	116.0	15.6
2T-9	<u>115.0</u>	<u>15.9</u>
Average	115.0	15.8
<u>Longitudinal at 800 F</u>		
2L-10	107.0	14.4
2L-11	105.0	14.7
2L-12	<u>105.0</u>	<u>14.7</u>
Average	105.7	14.6
<u>Transverse at 800 F</u>		
2T-10	106.0	14.7
2T-11	106.0	14.7
2T-12	<u>107.0</u>	<u>14.4</u>
Average	106.3	14.6

TABLE XXXI. SHEAR TEST RESULTS FOR SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr ALLOY PLATE AT ROOM TEMPERATURE

Specimen Number	Ultimate Shear Strength, ksi
<u>Longitudinal</u>	
4L-1	103.0
4L-2	114.0
4L-3	107.0
4L-4	<u>109.0</u>
Average	108.3
<u>Transverse</u>	
4T-1	108.0
4T-2	109.0
4T-3	109.0
4T-4	<u>106.0</u>
Average	108.0

TABLE XXXII. IMPACT TEST RESULTS FOR SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr ALLOY PLATE AT ROOM TEMPERATURE

Specimen Number	Energy, ft./lbs.
<u>Longitudinal</u>	
10L-1	14.0
10L-2	13.0
10L-3	13.0
10L-4	15.0
10L-5	15.0
10L-6	<u>13.0</u>
Average	13.9
<u>Transverse</u>	
10T-1	16.0
10T-2	15.0
10T-3	16.5
10T-4	17.0
10T-5	16.0
10T-6	<u>17.0</u>
Average	16.3

TABLE XXXIII. RESULTS OF SLOW-BEND TYPE FRACTURE TOUGHNESS TESTS ON SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr PLATE

Specimen Number	w, inches	a, inches	T, inches	P, lbs.	Span, inches	$f(\frac{a}{w})$	$K_Q^{(a)}$
<u>Longitudinal (L-T)</u>							
6L-1	1.500	0.746	0.750	7,600	6.0	2.64	87.4
6L-2	1.500	0.783	0.750	7,200	6.0	2.86	89.8
6L-3	1.500	0.723	0.750	7,950	6.0	2.52	87.1
6L-4	1.500	0.763	0.750	7,350	6.0	2.74	87.7
<u>Transverse (T-L)</u>							
6T-1	1.500	0.770	0.750	7,650	6.0	2.78	92.7
6T-2	1.500	0.777	0.750	7,550	6.0	2.82	92.9
6T-3	1.500	0.770	0.750	8,025	6.0	2.78	97.2

(a) Candidate K_Q values are invalid as K_{Ic} values since they do not meet the rigorous standard of $a, T, < 2.5 (\frac{K_Q I_c}{TYS})^2$. However, they do exceed a $2.2 (\frac{K_Q}{TYS})^2$ and as such should be considered marginally valid.

TABLE XXXIV. AXIAL LOAD FATIGUE TEST RESULTS FOR UNNOTCHED SOLUTION-TREATED AND AGED Ti-6Al-2Sn-2Mo-2Cr ALLOY PLATE (TRANSVERSE)

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-6	160.0	7,600
5-5	150.0	23,300
5-4	140.0	189,600
5-3	130.0	208,900
5-2	120.0	302,400
5-7	115.0	424,400
5-8	110.0	1,087,800
5-9	105.0	818,800
5-10	100.0	1,767,200
5-1	90.0	1,616,800
5-11	80.0	5,855,600
5-27	70.0	13,625,400 ^(a)
<u>400 F</u>		
5-12	150.0	7,100
5-13	140.0	12,000
5-14	130.0	21,400
5-15	120.0	178,500
5-16	110.0	369,000
5-17	100.0	829,500
5-18	90.0	2,142,600
5-19	80.0	3,059,600
5-24	70.0	10,144,000 ^(a)
<u>600 F</u>		
5-28	140.0	(b)
5-29	130.0	9,000
5-20	120.0	16,700
5-21	110.0	458,800
5-22	100.0	1,341,600
5-23	90.0	2,653,700
5-25	80.0	4,227,400
5-26	70.0	10,305,400 ^(a)

(a) Did not fail.

(b) Failed on loading.

TABLE XXXV. AXIAL LOAD FATIGUE TEST RESULTS FOR NOTCHED
($K_t=3.0$) SOLUTION-TREATED AND AGED Ti-6Al-
2Zr-2Sn-2Mo-2Cr ALLOY PLATE (TRANSVERSE)

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-31	120.0	1,590
5-32	100.0	5,780
5-33	90.0	7,700
5-34	80.0	11,100
5-38	75.0	24,800
5-35	70.0	133,400
5-36	60.0	400,250
5-37	50.0	813,600
5-41	45.0	1,135,800
5-40	40.0	10,624,900 ^(a)
<u>400 F</u>		
5-46	75.0	9,500
5-47	70.0	27,600
5-48	65.0	39,900
5-49	60.0	67,000
5-50	55.0	124,000
5-51	50.0	1,846,000
5-53	40.0	1,568,200
5-54	30.0	16,000,000 ^(a)
<u>600 F</u>		
5-39	80.0	2,530
5-40	70.0	9,100
5-42	60.0	25,480
5-45	55.0	361,150
5-43	50.0	366,120
5-53	40.0	1,417,600
5-55	30.0	14,718,600 ^(a)

(a) Did not fail.

TABLE XXXVI. SUMMARY DATA ON CREEP AND RUPTURE PROPERTIES FOR SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr ALLOY PLATE (TRANSVERSE)

Specimen Number	Stress, ksi	Temperature, F	Hours to Indicated Creep Deformation, percent				Initial Strain, percent	Rupture Time, hours	Elongation in 2 Inches, percent	Reduction of Area, percent	Minimum Creep Rate, percent
			0.1	0.2	0.5	1.0					
3-4	142	400	--	--	--	--	On Loading	13.6	47.7	--	
3-5	137	400	0.01	0.03	0.7	3.725	353.7 (b)	4.302	--	0.00005	
3-6	120	400	0.10	550	--	1.180	574.5	1.400	--	0.00004	
3-2	133	600	--	--	-- (a)	--	On Loading	--	--	--	
3-3	128	600	0.05	10	4000 (a)	2.980	643.9 (b)	3.280	--	0.000055	
3-10	120	600	3.5	100	--	1.940	382.3 (b)	2.168	--	--	
3-7	110	600	1350 (a)	--	--	1.260	365.7 (b)	1.332	--	--	
3-11	130	800	--	--	--	--	On Loading	13.6	48.3	--	
3-9	120	800	0.1	0.3	1.5	2.408	504.9 (b)	11.2	21.5	--	
3-8	100	800	6	10 (a)	175 (a)	0.992	504.4 (b)	1.731	--	0.0004	
3-1	50	800	320	2200 (a)	7500 (a)	0.456	841.0 (b)	0.584	--	0.000056	

(a) Estimate.

(b) Test discontinued.

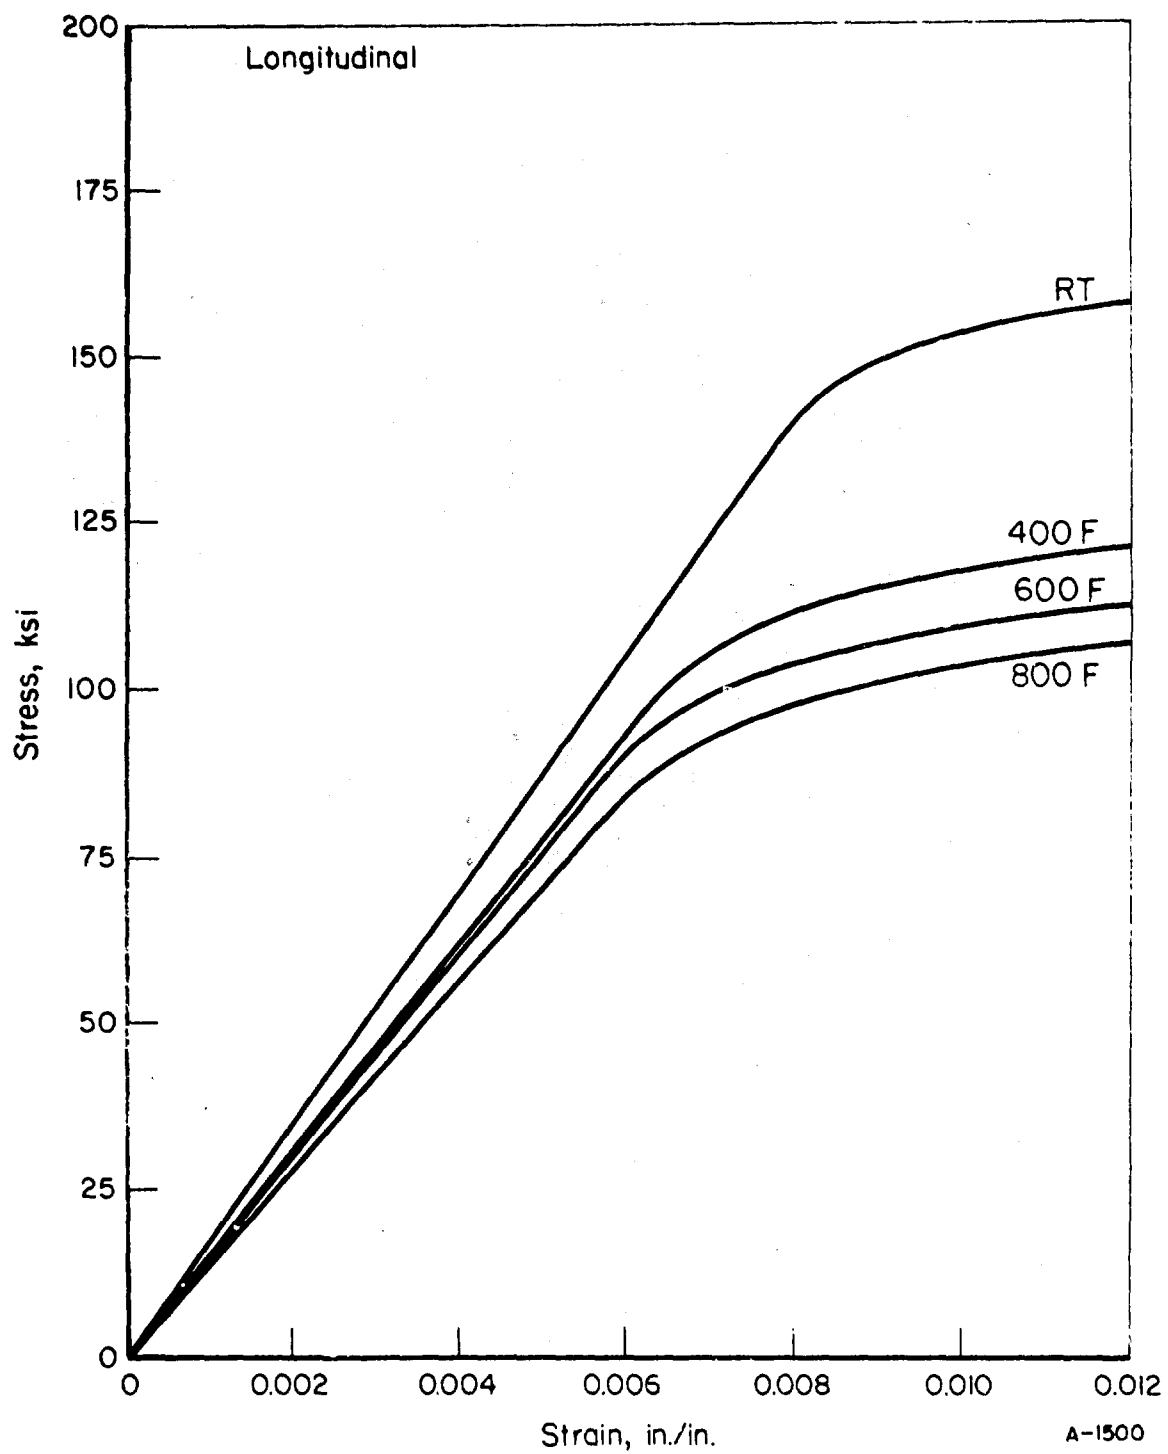


FIGURE 42. TYPICAL TENSILE STRESS-STRAIN CURVES AT TEMPERATURE FOR SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr PLATE (LONGITUDINAL)

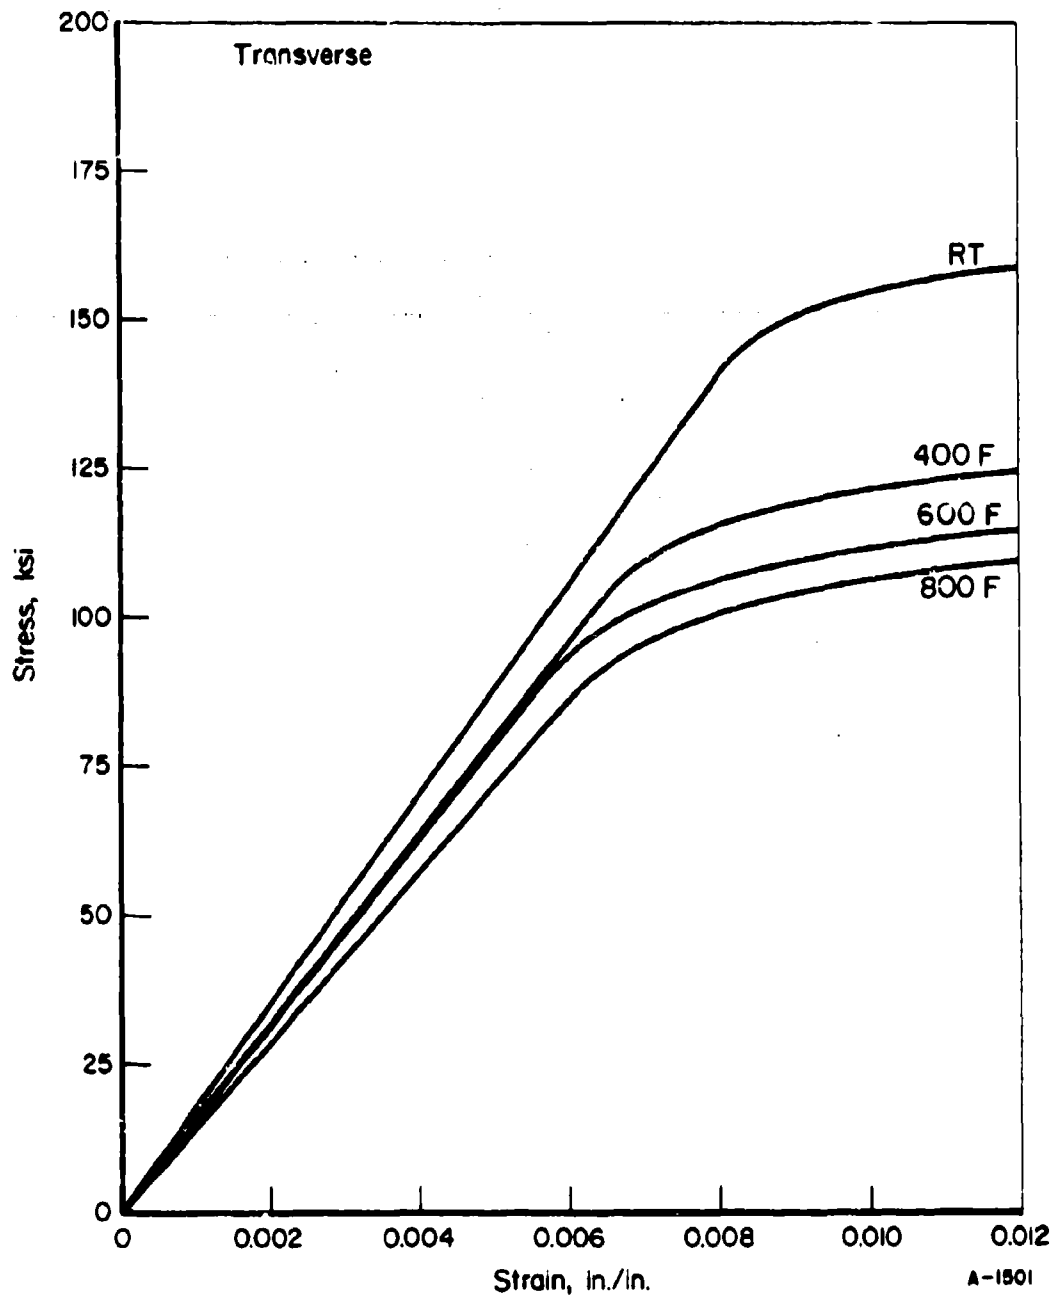


FIGURE 43. TYPICAL TENSILE STRESS-STRAIN CURVES AT TEMPERATURES FOR SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr PLATE (TRANSVERSE)

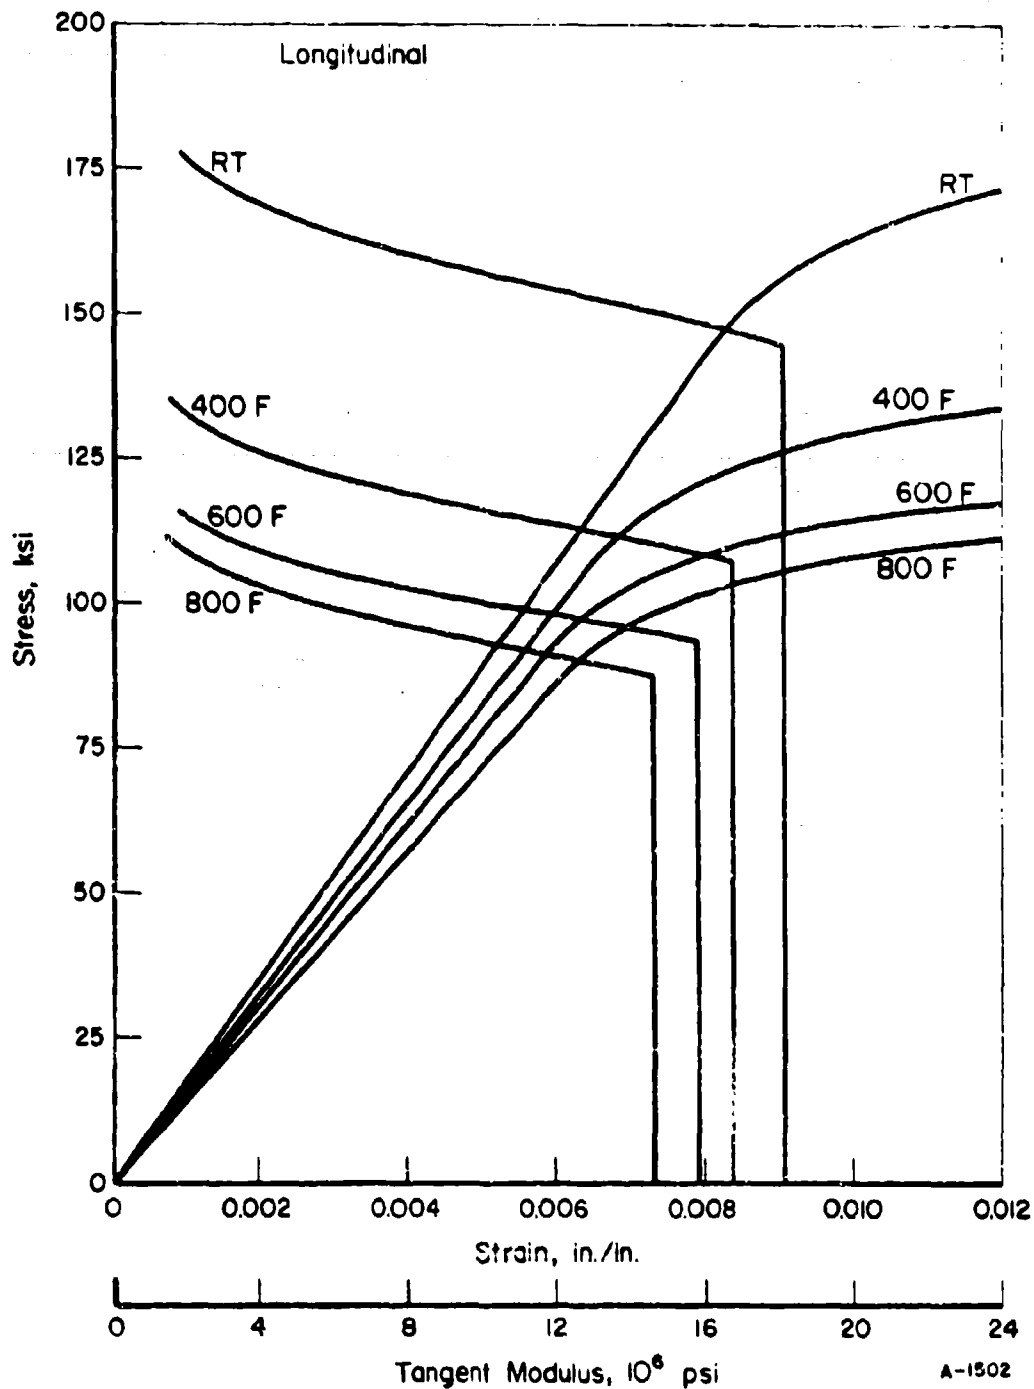


FIGURE 44. TYPICAL COMPRESSIVE STRESS-STRAIN AND TANGENT-MODULUS CURVES FOR SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr PLATE (LONGITUDINAL)

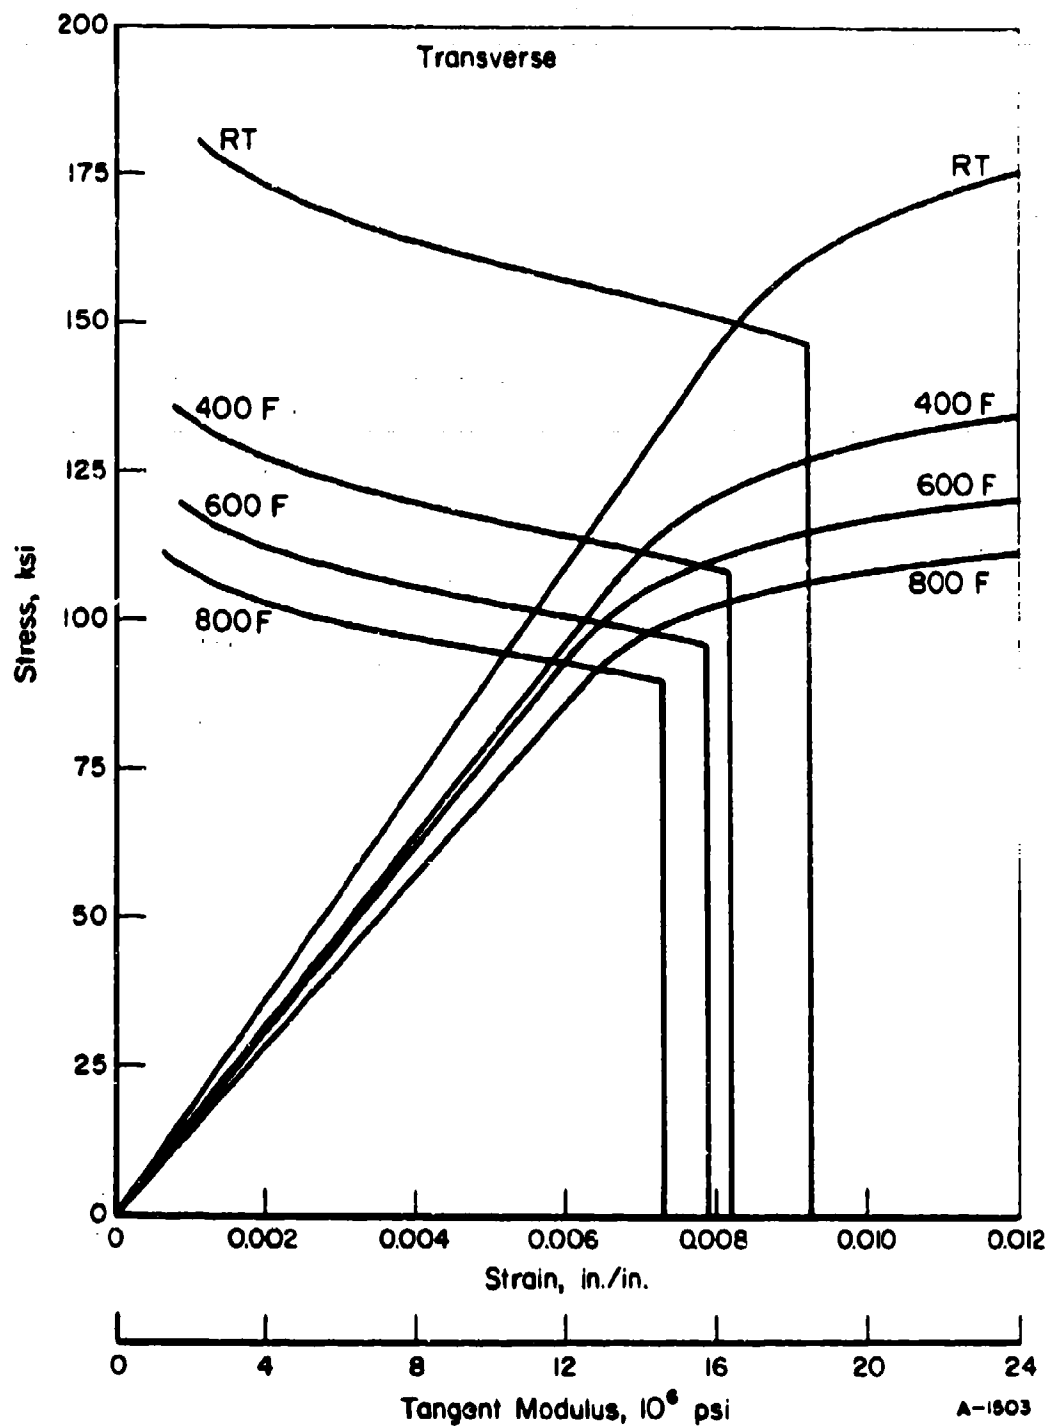


FIGURE 45. TYPICAL COMPRESSIVE STRESS-STRAIN AND TANGENT-MODULUS CURVES FOR SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr PLATE (TRANSVERSE)

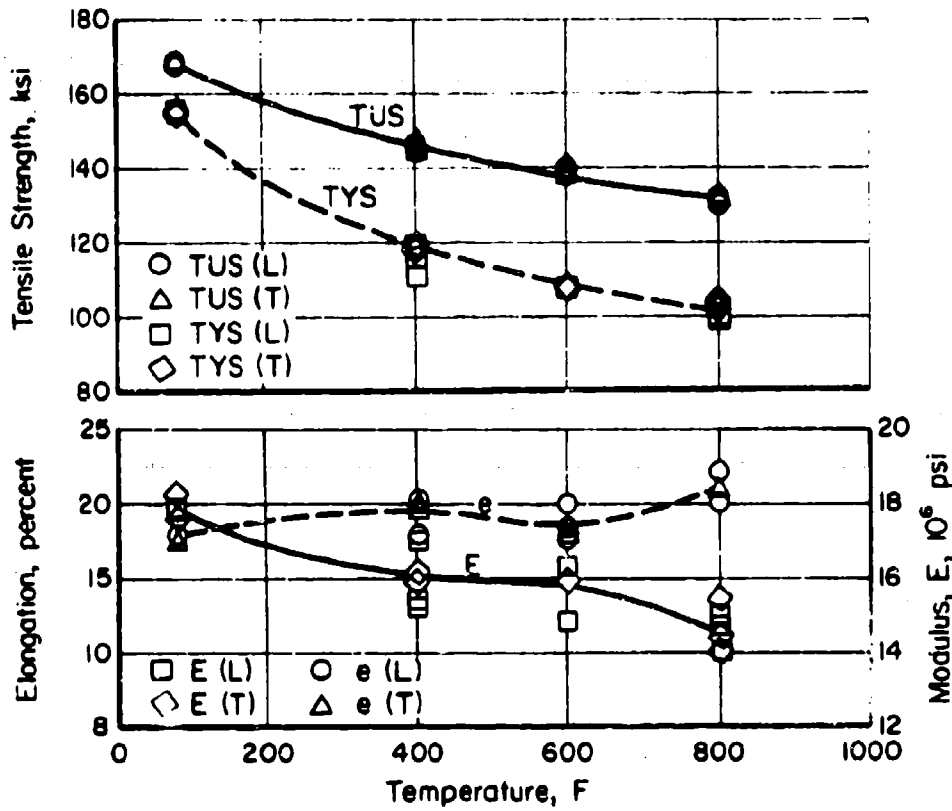


FIGURE 46. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr PLATE

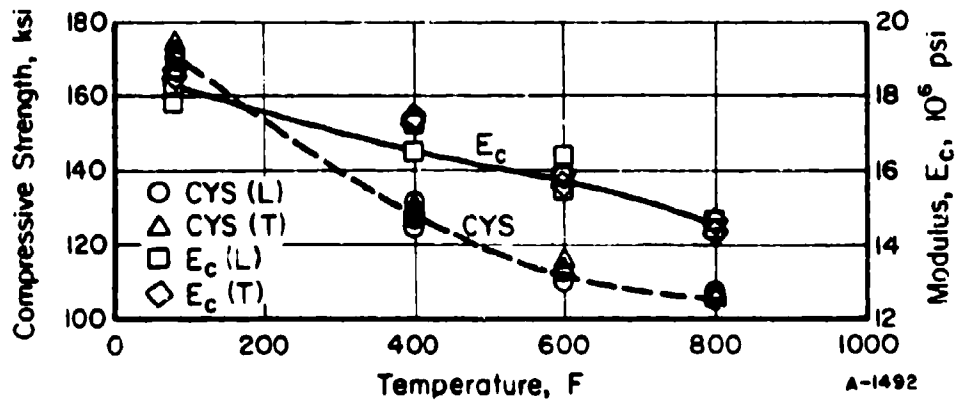


FIGURE 47. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr PLATE

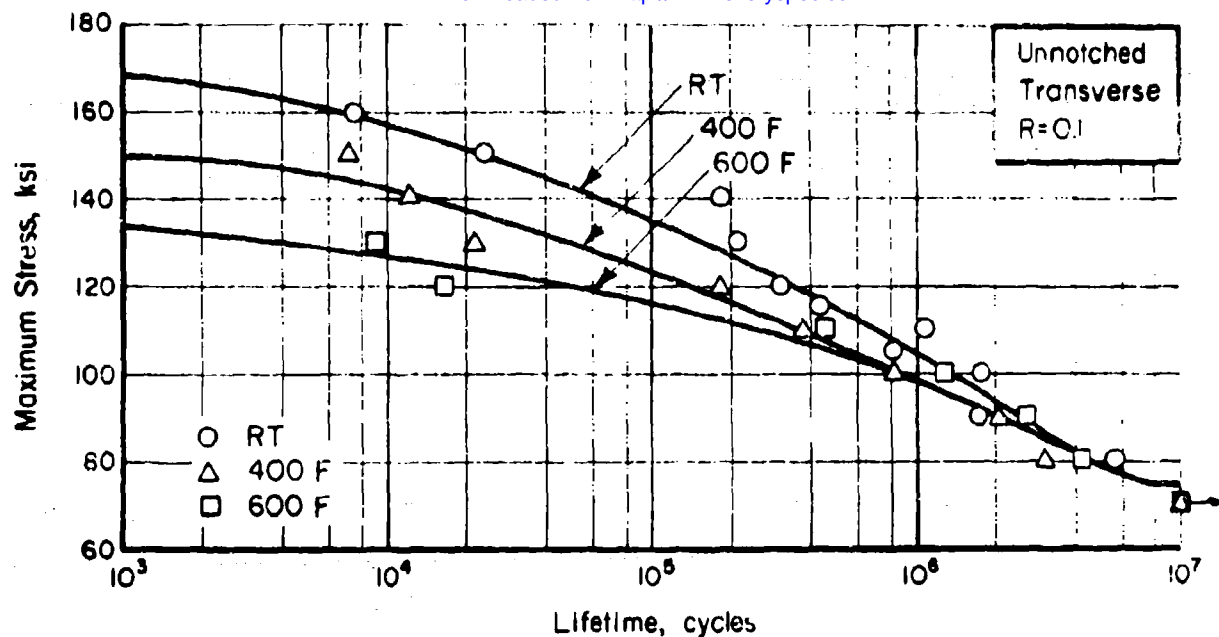


FIGURE 48. AXIAL LOAD FATIGUE BEHAVIOR OF UNNOTCHED SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr PLATE (TRANSVERSE)

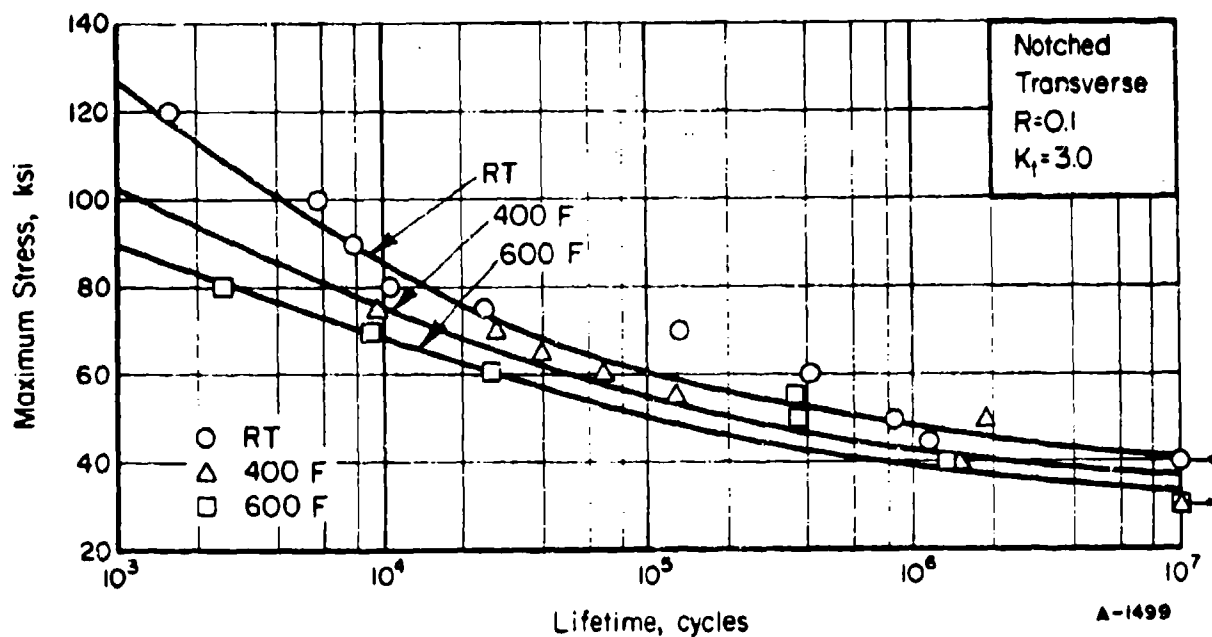


FIGURE 49. AXIAL LOAD FATIGUE BEHAVIOR OF NOTCHED ($K_t = 3.0$) SOLUTION-TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr PLATE (TRANSVERSE)

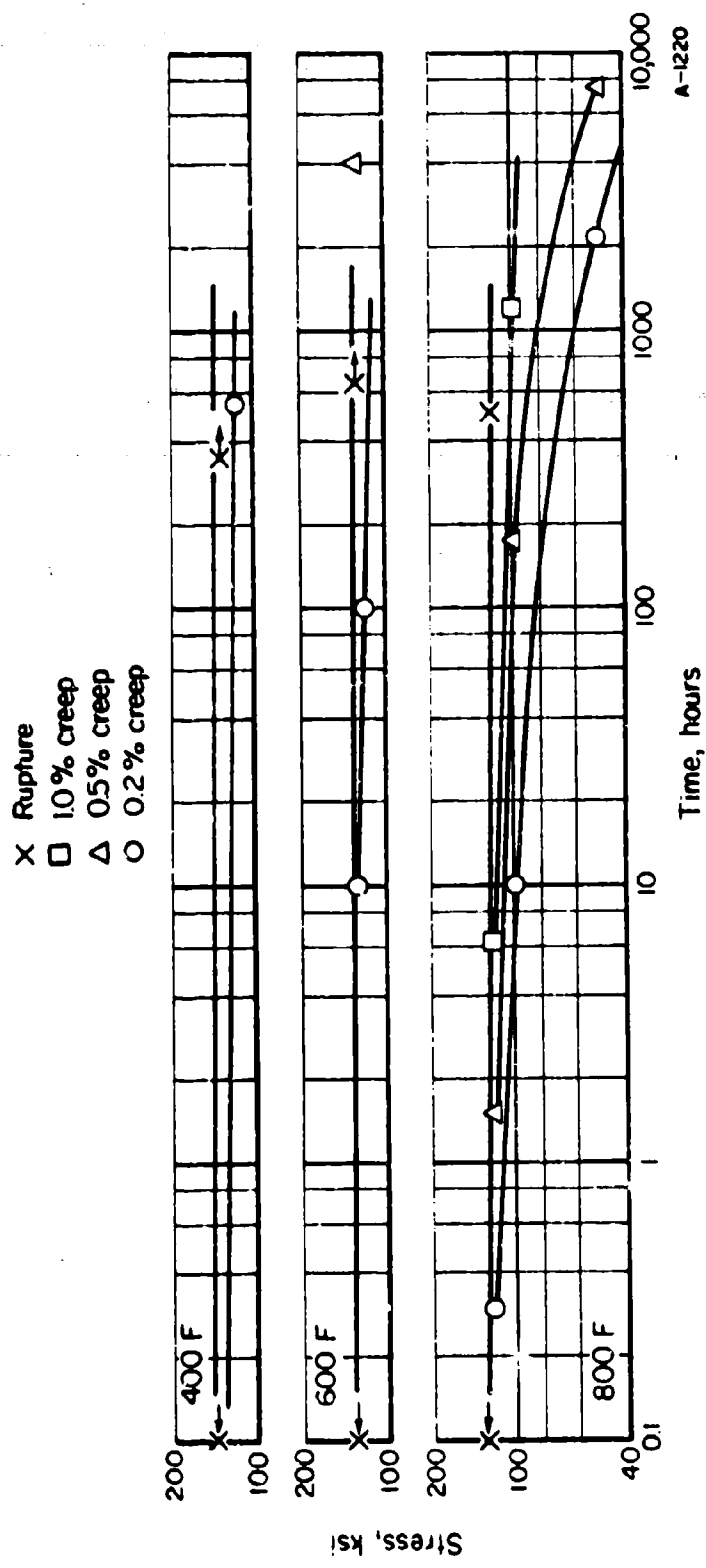


FIGURE 50. STRESS-RUPTURE AND PLASTIC DEFORMATION CURVES FOR SOLUTION TREATED AND AGED Ti-6Al-2Zr-2Sn-2Mo-2Cr PLATE (TRANSVERSE)

Ti-6Al-6V-2Sn Isothermal Die ForgingsMaterial Description

This is a heat-treatable alpha-beta type alloy similar in many respects to Ti-6Al-4V, but containing increased content of beta-stabilizing elements which provide higher strength potential.

The material used for this evaluation was made by IIT Research Institute under Air Force Contract F33615-67-C-1722. It consisted of structural shapes and nose wheels that were isothermally creep (slow speed) forged from flat preforms machined from conventionally forged Ti-6Al-6V-2Sn alloy billets.

Processing and Heat Treating

The material was received with no heat treatment after forging. Specimens were solution treated at 1650 F for 1/2 hour, water quenched, and aged at 1050 F for 4 hours and air cooled as suggested by IIT Research Institute. Other heat treatments designed for lower UTS and higher toughness should be considered for other applications.

Since the material was of complex shapes, it was necessary to cut specimens from various positions and no specimen layout drawing is shown.

Test Results

Tension. Test results for transverse specimens at room temperature, 400 F, 700 F, and 900 F are given in Table XXXVII. Typical stress-strain curves at temperature are presented in Figure 51. Effect of temperature curves are shown in Figure 53.

Compression. Results of tests on transverse specimens at room temperature, 400 F, 700 F, and 900 F are given in Table XXXVIII. Typical stress-strain and tangent-modulus curves at temperature are shown in Figure 52. Effect of temperature curves are shown in Figure 54.

Shear. Pin shear test results at room temperature for longitudinal and transverse specimens are given in Table XXXIX.

Impact. Test results for longitudinal and transverse specimens at room temperature are given in Table XL.

Fracture Toughness. Slow-bend tests were attempted, but the material thickness was not sufficient to obtain large specimens. The candidate K_Q values did not meet ASTM criteria and are not reported. Results of tests on compact tension specimens at AFML are reported in the data sheet in Appendix III.

Fatigue. Axial load tests were conducted at room temperature, 400 F, and 700 F for both unnotched and notched transverse specimens at a stress ratio of $R = 0.1$. Tabular test results are given in Tables XLI and XLII. S-N curves are presented in Figures 55 and 56.

Creep and Stress Rupture. Test results for transverse specimens at 700 F and 900 F are given in Table XLIII. Tests were attempted at 400 F and 550 F, but no appreciable creep occurred. Log-stress versus log-time curves are presented in Figure 57.

Stress Corrosion. Tests were conducted as described in the experimental procedures section of this report. No failures or cracks occurred in the 1000-hour test duration.

Thermal Expansion. The coefficient of thermal expansion for this alloy is 5.3×10^{-6} in./in./F from 70 F to 900 F.

Density. The density value for this alloy is 0.164 lb./in.³.

TABLE XXXVII. TENSION TEST RESULTS FOR SOLUTION-TREATED AND AGED
Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGING (TRANSVERSE)

Specimen Number	Ultimate Tensile Strength, ksi	0.2 Percent Offset Yield Strength, ksi	Elongation, in 1 Inch, percent	Tensile Modulus, 10 ⁶ psi
<u>Room Temperature</u>				
5	203.3	194.1	3.0	14.9
6	199.6	188.6	7.0	16.0
13	204.5	196.1	4.0	17.0
Average	202.5	192.9	4.7	16.0
<u>400 F</u>				
7	171.6	154.8	7.0	15.4
8	174.0	152.0	9.0	14.1
9	165.5	152.7	7.0	14.7
Average	170.4	153.2	7.7	14.7
<u>700 F</u>				
10	154.7	134.4	12.0	13.0
11	155.7	132.8	8.0	13.3
12	164.8	128.2	5.0	13.0
Average	158.4	131.8	8.3	13.1
<u>900 F</u>				
15	137.4	82.4	23.0	11.5
16	143.6	87.5	20.0	12.4
17	119.7	70.9	23.0	12.4
Average	133.6	80.3	22.0	12.1

TABLE XXXVIII. COMPRESSION TEST RESULTS FOR SOLUTION-TREATED AND AGED
Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS (TRANSVERSE)

Specimen Number	0.2 Percent Offset Yield Strength, ksi	Compression Modulus, 10 ³ psi
<u>Room Temperature</u>		
2T-1	202.6	18.0
2T-2	200.1	18.5
2T-3	195.2	17.6
	Average 199.3	Average 18.0
<u>400 F</u>		
2T-4	170.6	16.6
2T-5	172.2	16.0
2T-6	180.0	15.7
	Average 174.3	Average 16.1
<u>700 F</u>		
2T-7	156.6	12.0
2T-8	150.0	13.6
2T-9	152.3	14.0
	Average 152.9	Average 13.2
<u>900 F</u>		
2T-10	101.2	12.0
2T-11	110.0	12.2
2T-12	112.0	11.6
	Average 107.7	Average 11.9

TABLE XXXIX. SHEAR TEST RESULTS AT ROOM TEMPERATURE FOR SOLUTION-TREATED AND AGED Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS

Specimen Number	Ultimate Shear Strength, ksi
<u>Longitudinal</u>	
4L-1	131.0
4L-2	132.0
4L-3	131.7
4L-4	131.6
	Average
	131.6
<u>Transverse</u>	
4T-1	130.0
4T-2	130.0
4T-3	130.1
4T-4	130.0
	Average
	130.0

TABLE XL. IMPACT TEST RESULTS FOR SOLUTION-TREATED AND AGED Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS

Specimen Number	Energy, ft. lbs.
<u>Longitudinal</u>	
10L-1	12.0
10L-2	11.0
10L-3	11.0
10L-4	11.7
	Average
	11.7
<u>Transverse</u>	
10T-1	8.5
10T-2	9.0
10T-3	8.0
10T-4	8.5
	Average
	8.5

TABLE XLI. AXIAL LOAD FATIGUE TEST RESULTS FOR
UNNOTCHED SOLUTION-TREATED AND AGED
Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-1	100.0	4,700
5-2	100.0	15,300
5-3	90.0	15,500
5-4	80.0	15,300
5-6	70.0	19,900
5-5	60.0	25,800
5-7	50.0	35,990
5-17	40.0	12,679,200 ^(a)
<u>400 F</u>		
5-8	80.0	15,900
5-9	70.0	19,900
5-10	60.0	100,400
5-11	50.0	30,700
5-18	40.0	100,700
5-19	30.0	10,452,600 ^(a)
<u>700 F</u>		
5-12	80.0	18,000
5-13	70.0	30,200
5-14	60.0	27,500
5-15	60.0	38,900
5-16	50.0	3,161,100 ^(b)
5-20	40.0	11,436,800 ^(a)

(a) Did not fail.

(b) Grip failure.

TABLE XLII. AXIAL LOAD FATIGUE TEST RESULTS FOR NOTCHED ($K_t = 3.0$) SOLUTION-TREATED AND AGED Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS

Specimen Number	Maximum Stress, ksi	Lifetime, cycles
<u>Room Temperature</u>		
5-35	70.0	3,900
5-31	60.0	16,200
5-32	50.0	26,300
5-33	40.0	244,000
5-34	30.0	8,134,400
5-21	25.0	10,189,800 ^(a)
<u>400 F</u>		
5-37	70.0	9,400
5-38	60.0	18,200
5-40	55.0	26,600
5-39	50.0	662,200
5-41	45.0	61,200
5-36	40.0	4,784,900
5-20	35.0	10,160,400 ^(a)
<u>700 F</u>		
5-42	65.0	6,100
5-43	60.0	7,800
5-44	55.0	19,700
5-45	50.0	56,400
5-46	45.0	120,700
5-47	40.0	86,000
5-48	35.0	1,110,500
5-49	30.0	14,219,800 ^(a)

(a) Did not fail.

TABLE XLIII. SUMMARY DATA ON CREEP AND RUPTURE PROPERTIES FOR SOLUTION-TREATED AND AGED Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS (TRANSVERSE)

Specimen Number	Stress, ksi	Temperature, F	Hours to Indicated Creep Deformation, percent					Initial Strain, percent	Rupture Time, hours	Elongation in 2 in., percent	Reduction of Area, percent	Minimum Creep Rate, percent
			0.1	0.2	0.5	1.0	2.0					
3-1	153.3	700	--	--	--	--	--	On Loading	8.9	24.8	--	
3-4	145	700	--	--	0.07	0.25	0.70	2.6	13.8	32.6	1.5	
3-5	135	700	0.08	0.2	0.8	2.5	11.0	59.8 (b)	18.5	45.3	0.13	
3-6	110	700	0.3	1.0	12	47	180	1007.8 (b)	6.96	--	0.0050	
3-8	50	700	17	75	1000 (a)	--	--	122.8 (b)	0.465	--	--	
3-9	25	700	120	1450	7500 (a)	--	--	935.5 (b)	0.246	--	0.000075	
3-2	60	900	0.07	0.15	0.7	2.0	5.2	27.6	33.9	73.2	0.31	
3-7	30	900	0.30	1.0	6.0	28	77	624.3 (b)	48.5	81.0	0.020	
3-10	8	900	5.5	25	77 (a)	--	--	119.8 (b)	0.469	--	--	
3-11	3	900	100	125	5000 (a)	--	--	937.5 (b)	0.377	--	0.000075	

(a) Estimate.

(b) Test discontinued.

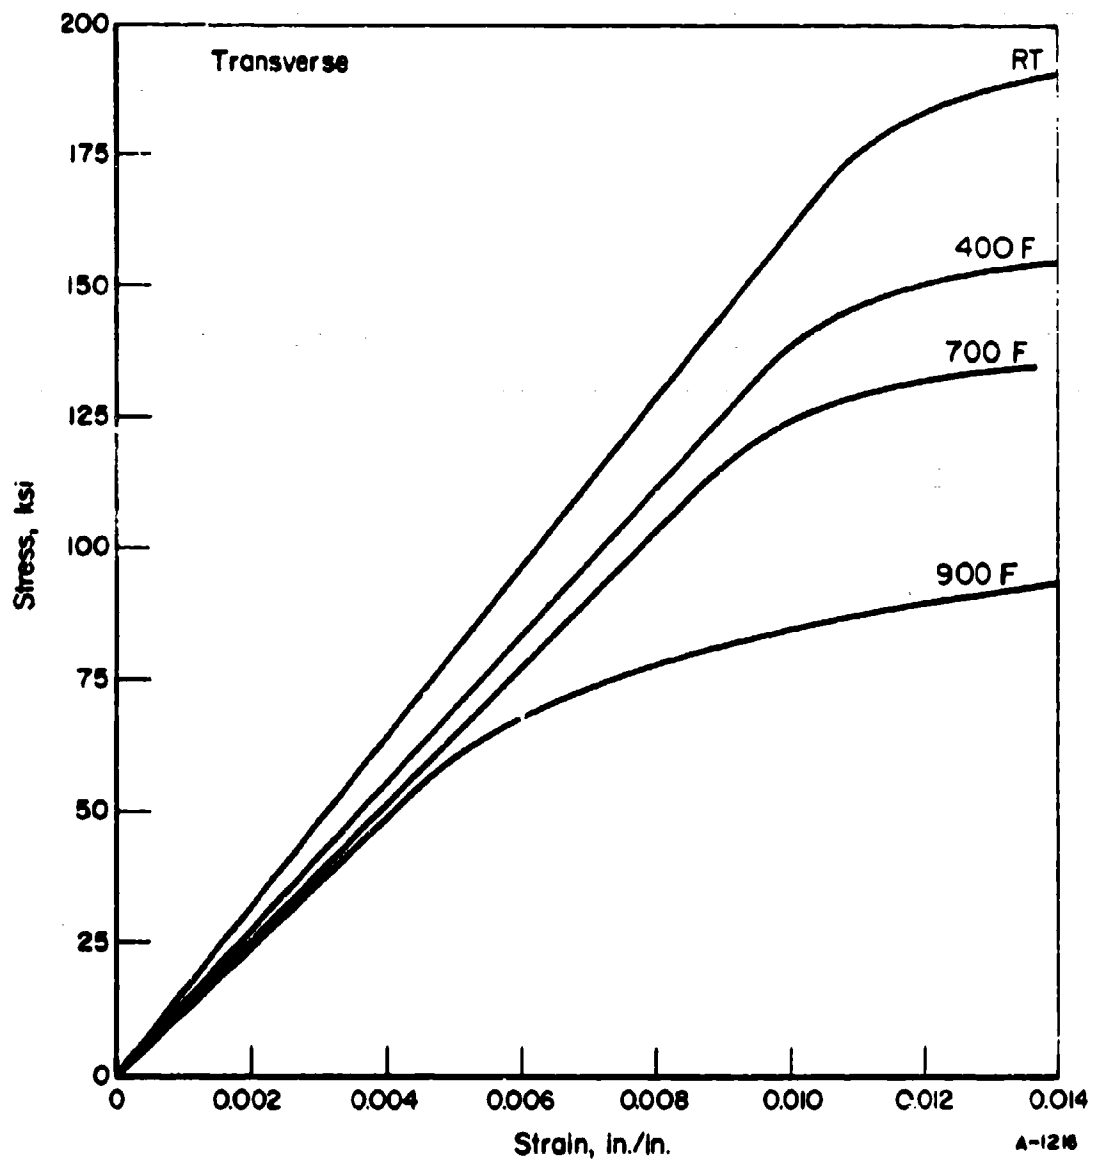


FIGURE 51. TYPICAL TENSILE STRESS-STRAIN CURVES FOR SOLUTION TREATED AND AGED Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS

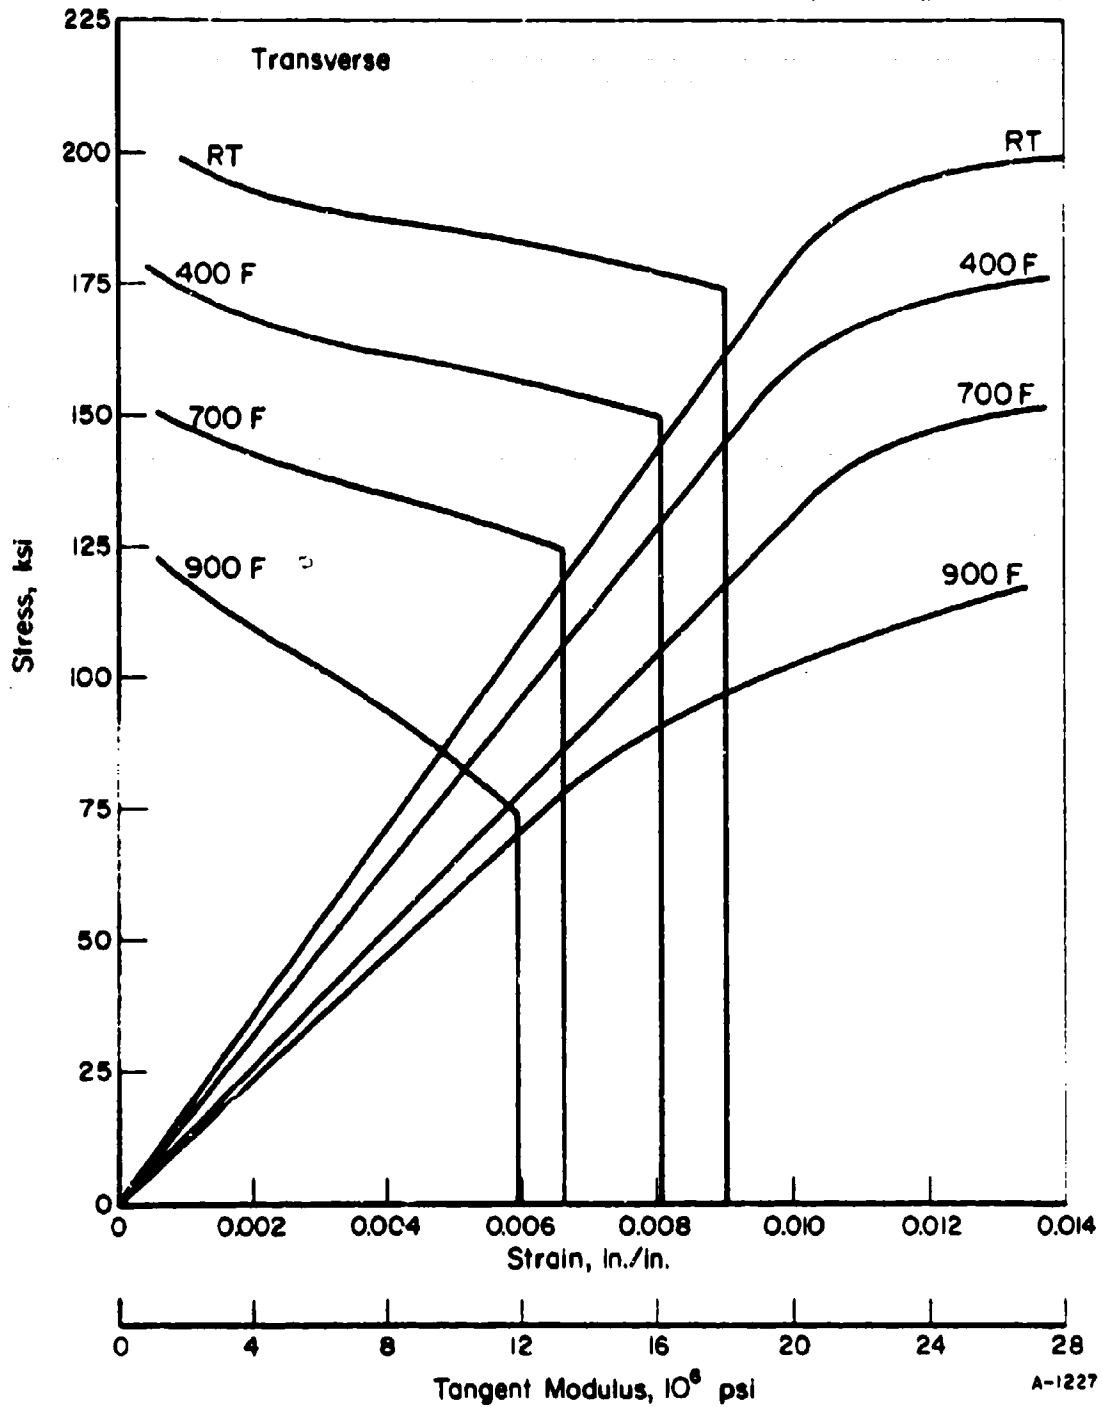


FIGURE 52. TYPICAL COMPRESSIVE STRESS-STRAIN AND TANGENT-MODULUS CURVES FOR SOLUTION TREATED AND AGED Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS

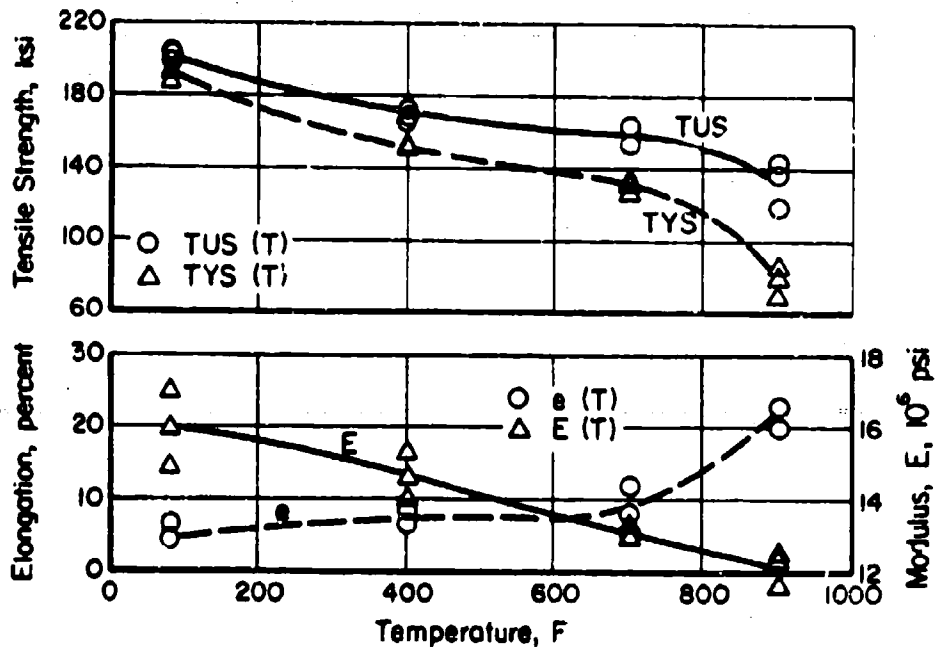


FIGURE 53. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF SOLUTION TREATED AND AGED T1-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS

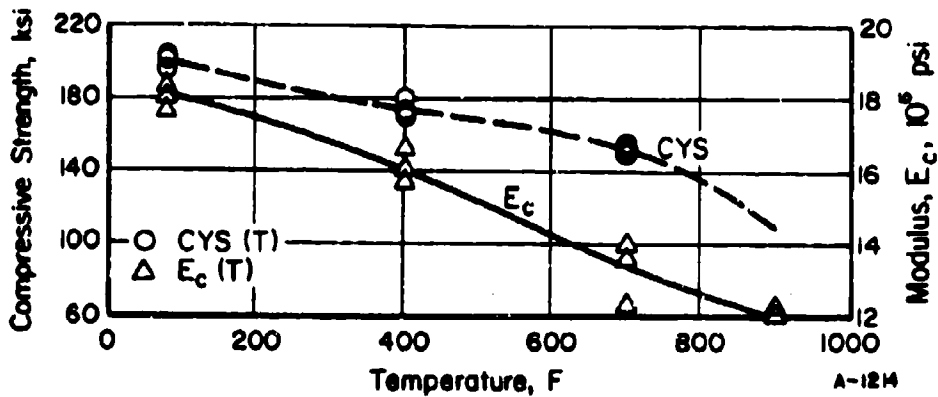


FIGURE 54. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF SOLUTION TREATED AND AGED T1-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS

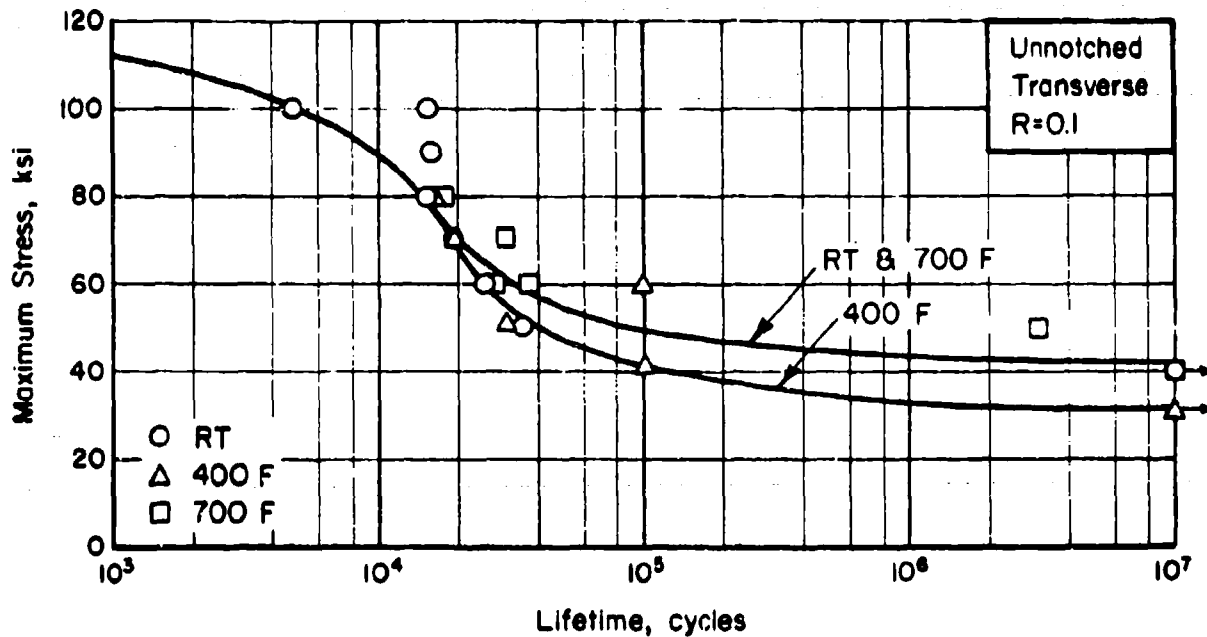


FIGURE 55. AXIAL LOAD FATIGUE BEHAVIOR OF UNNOTCHED SOLUTION-TREATED AND AGED Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS (TRANSVERSE)

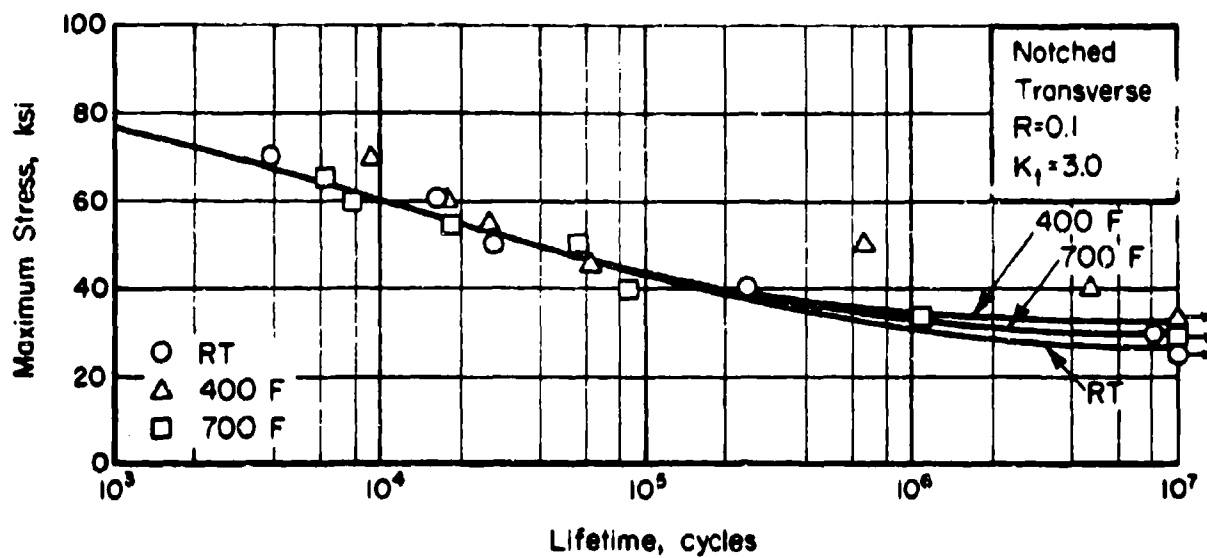


FIGURE 56. AXIAL LOAD FATIGUE BEHAVIOR OF NOTCHED ($K_t = 3.0$) SOLUTION-TREATED AND AGED Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS (TRANSVERSE)

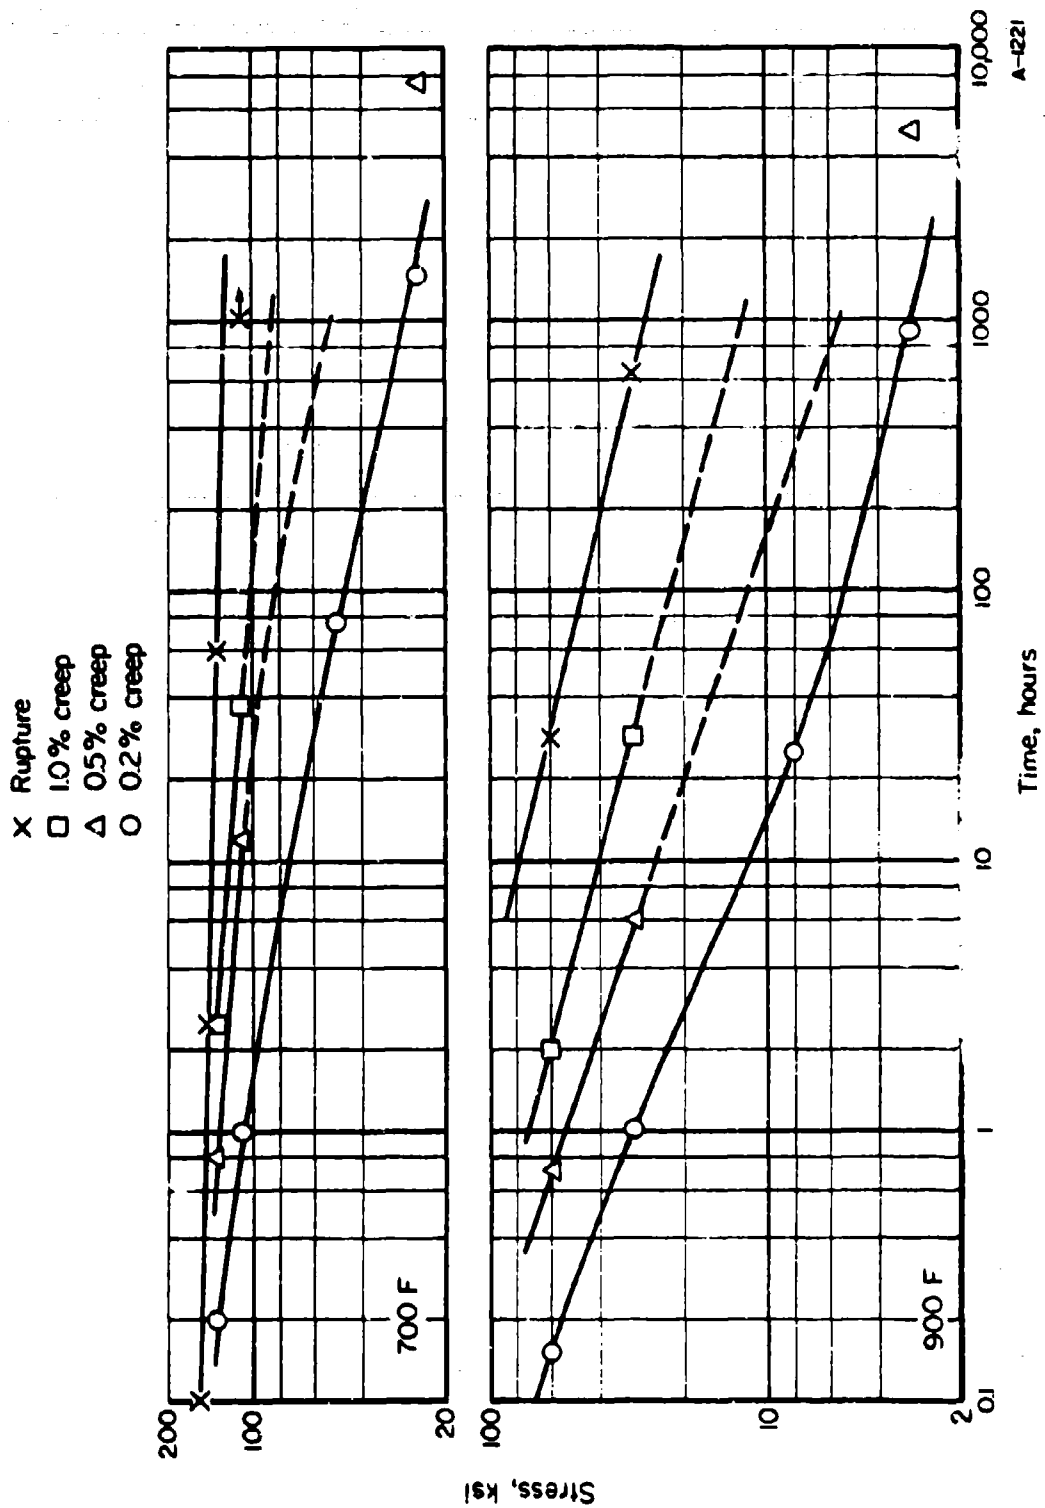


FIGURE 57. STRESS RUPTURE AND PLASTIC DEFORMATION CURVES FOR SOLUTION TREATED AND AGED Ti-6Al-6V-2Sn ISOTHERMAL DIE FORGINGS

DISCUSSION OF PROGRAM RESULTS


The tendency in an evaluation program of this type is to compare the materials property information obtained with similar data on materials already in use. Whether such a comparison should be the deciding factor for interest in a newer alloy is open to question. Many criteria, such as forming characteristics, weldability, oxidation resistance, etc., can be of particular importance so that strength properties may become secondary. However, since first comparisons are usually made on the basis of mechanical strength (tensile ultimate and tensile yield), the data generated on this program are compared to information for similar alloys. Figures 58 and 59 are effect-of-temperature curves concerned with these properties.

CONCLUSIONS

The objective of this program was the generation of useful engineering data for newly developed materials. During the contract term, the following materials were evaluated


- (1) X2048-T851 Plate
- (2) 7050-T73651 Plate
- (3) 21-6-9 Annealed Sheet
- (4) Ti-8Mo-8V-2Fe-3Al (STA) Sheet
- (5) Ti-6Al-2Zr-2Sn-2Mo-2Cr (STA) Plate
- (6) Ti-6Al-6V-2Sn STA Isothermal Die Forgings.

A data sheet was issued for each material. As a summary, each of the data sheets is reproduced in Appendix III.

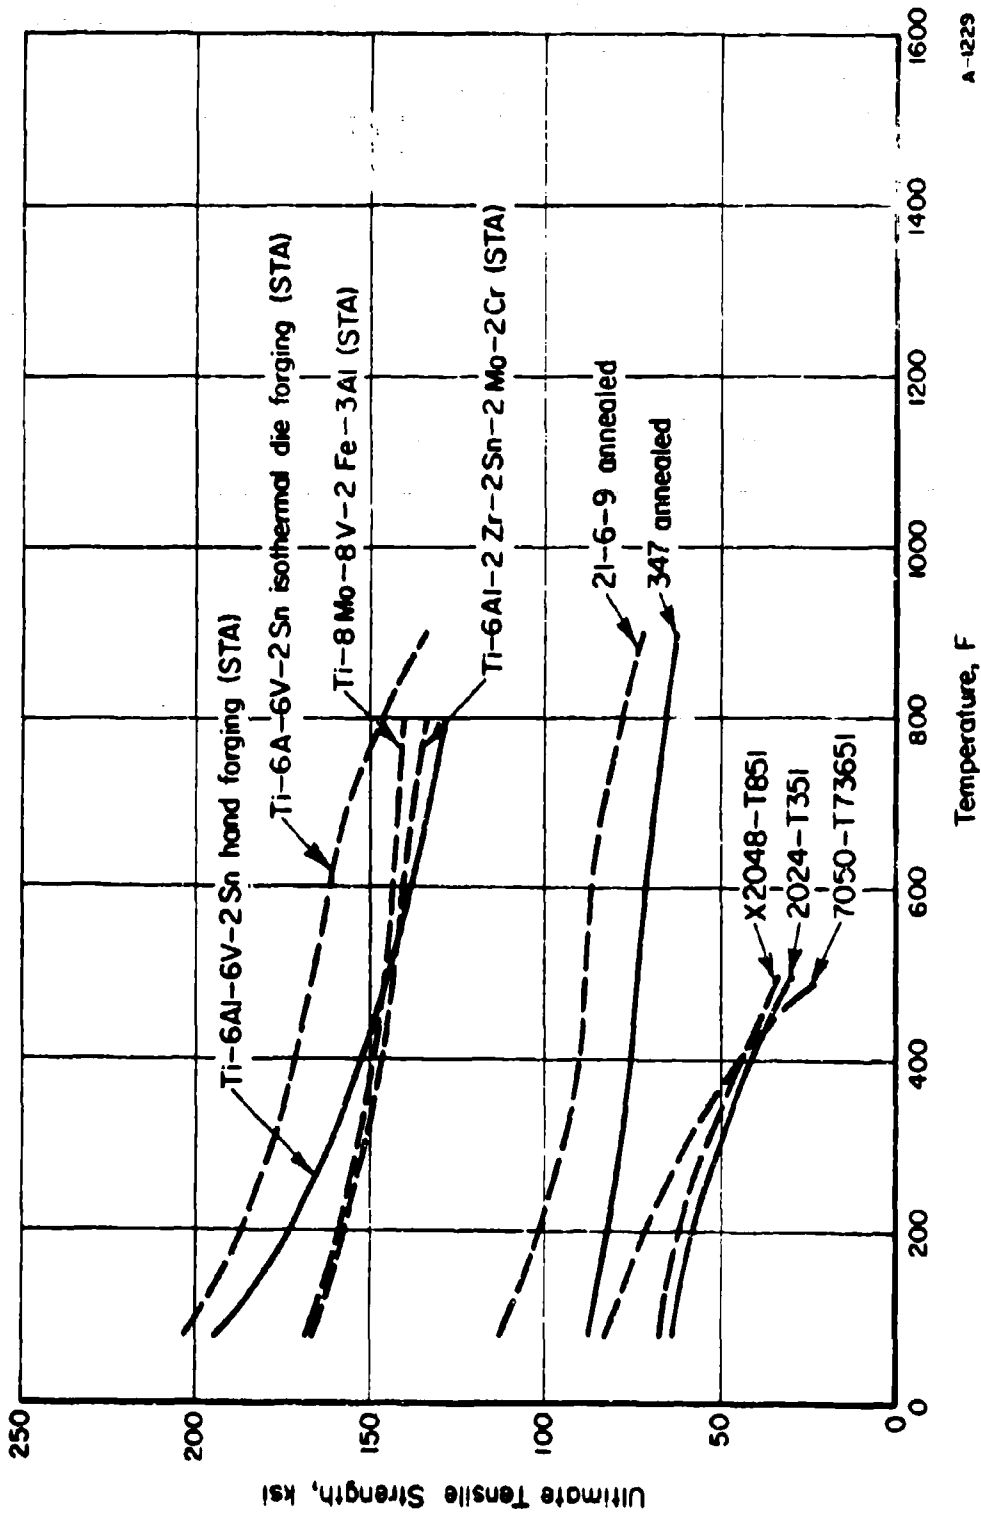

A-1229

FIGURE 58. TENSILE ULTIMATE STRENGTH AS A FUNCTION OF TEMPERATURE

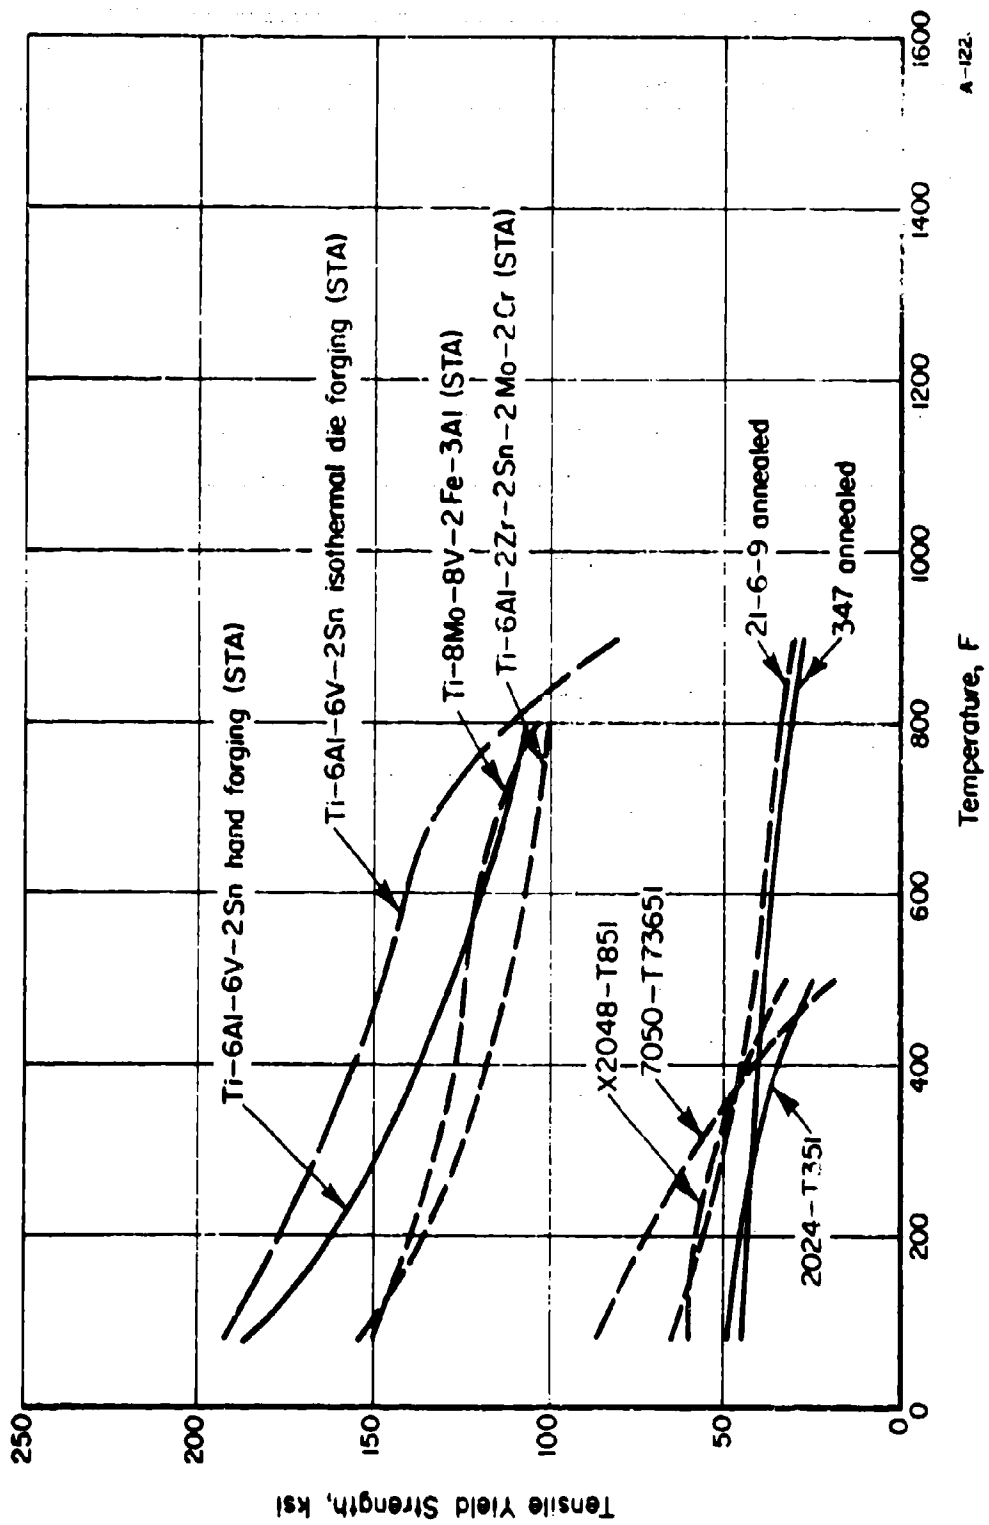

A-122.

FIGURE 59. TENSILE YIELD STRENGTH AS A FUNCTION OF TEMPERATURE

APPENDIX I
EXPERIMENTAL PROCEDURE

APPENDIX I

EXPERIMENTAL PROCEDUREMechanical Properties

The various mechanical properties of interest for each of the materials are as follows:

- (1) Tension
 - (a) Tensile ultimate strength, TUS
 - (b) Tensile yield strength, TYS
 - (c) Elongation, e_t
 - (d) Reduction in area, RA
 - (e) Modulus of elasticity, E_t .
- (2) Compression
 - (a) Compressive yield strength, CYS
 - (b) Modulus of elasticity, E_c .
- (3) Creep and stress-rupture
 - (a) Stress for 0.2 or 0.5 percent deformation in 100 hours and 1000 hours
 - (b) Stress for rupture in 100 hours and 1000 hours.
- (4) Shear
 - (a) Shear ultimate strength, SUS
- (5) Axial fatigue*
 - (a) Unnotched, $R = 0.1$, lifetime: 10^3 through 10^7 cycles

* "R" represents the algebraic ratio of the minimum stress to the maximum stress in one cycle; that is, $R = S_{min}/S_{max}$. " K_t " represents the Neuber-Peterson theoretical stress concentration factor.

- (b) Notched ($K_t = 3.0$), $R = 0.1$, lifetime: 10^3 through 10^7 cycles.
- (6) Fracture toughness, K_{Ic} or K_c
- (7) Stress corrosion
 - (a) 80 percent TYS for 1000 hours maximum, 3-1/2 percent NaCl solution.
- (8) Thermal expansion.
- (9) Bend
 - (a) Minimum radius.
- (10) Impact
 - (a) Charpy V-notch.
- (11) Density.

Specimen Identification

A simple system of numbers and letters was used for specimen identification. Coding consisted of a number indicating the type of test and also indicating a comparable area on the sheet, plate, or forging. For certain test types, the number was followed by a letter signifying specimen orientation (L for longitudinal, T for transverse, ST for short transverse). The test types where the letter did not appear were creep, fatigue, and bend since, in these cases, only one specimen orientation was used. The next number in the coding specifies the location from which the specimen blank was taken from the original material configuration. Coding was as follows:

<u>Assigned Number</u>	<u>Test Type</u>
1	Tension
2	Compression
3	Creep and stress-rupture
4	Shear
5	Fatigue
6	Fracture toughness

<u>Assigned Number</u>	<u>Test Type</u>
7	Stress corrosion
8	Thermal expansion
9	Bend
10	Impact
11	Density

As an example, a specimen numbered 2-T5 is a compression specimen, transverse orientation, cut from Location 5. Also, a specimen numbered 5-12 is a fatigue specimen cut from Location 12.

Test Description

Tension

Procedures used for tension testing are those recommended in ASTM methods E8-68 and E21-66T as well as in Federal Test Method standard No. 151a (method 211.1). Six specimens (three longitudinal and three transverse) were tested at each temperature to determine ultimate tensile strength, 0.2 percent offset yield strength, elongation, and reduction in area. The modulus of elasticity was obtained from load-strain curves plotted by an autographic recorder during each test.

All tensile tests were carried out in Baldwin Universal testing machines. These machines are calibrated at frequent intervals in accordance with ASTM method E4-64 to assure loading accuracy within 0.2 percent. The machines are equipped with integral automatic strain pacers and autographic strain recorders.

Specimens tested at elevated temperatures were heated in standard wire-wound resistance-type furnaces. Each furnace was equipped with a Foxboro controller capable of maintaining the test temperature to within 5 F of the control temperature over a 2-inch gage length. Chromel-Alumel thermocouples attached to the specimen gage section were used to monitor temperatures. Each specimen was soaked at temperature at least 20 minutes before being tested.

An averaging-type linear differential transformer extensometer was used to measure strain. For elevated temperature testing, the extensometer was equipped with extensions to bring the transformer unit out of the furnace. The extensometer conformed to ASTM E3-64T Classification B1 having a sensitivity of 0.0001 inch/inch. The strain rate in the elastic region was maintained at 0.005 inch/inch/minute. After yielding occurred, the head speed was increased to 0.1 inch/inch/minute until fracture.

Compression

Procedures for conducting compression tests are outlined in ASTM Method E9-67 along with temperature control provisions of E21-66T. All sheet and thin plate tests were carried out in Baldwin Universal testing machines using a North American type compression fixture as shown in Reference 2. Specimen heating was accomplished by a forced-air furnace for temperatures up to 1000 F. Specimen temperature was maintained by means of a Wheelco pyrometer. Three Chromel-Alumel thermocouples attached to the fixture were used to monitor temperatures to within 3 F of the test temperature. For higher temperatures, wire-wound furnaces were used with controls as described in the tensile test section.

The extensometer used for the compression tests was quite similar to that used in the tensile testing. The extension arms were fastened to the specimen at small notches spanning a 2-inch gage length. The output from the microformer was fed into a load-strain recorder to provide autographic load-strain curves. During testing the strain rate was adjusted to 0.005 inch/inch/minute.

For bar and forging material, cylindrical specimens similar to those described in ASTM E9-67 were used with appropriate temperature control and strain measurement as described above.

Six specimens (three longitudinal and three transverse) were tested at each temperature.

Shear

Single-shear sheet-type specimens were used for sheet and thin-plate material; for bar and forgings, a double-shear pin-type was used. Shear testing was performed at room temperature only. A minimum of six specimens (three longitudinal and three transverse) were used to determine ultimate shear strength.

Bend

The procedures for conducting bend tests are described in report MAB-192-M. The specimens were placed in a rigid three-point loading fixture and bending tips of various sizes were used to determine the minimum bend radius at room temperature.

Creep and Stress Rupture

Standard dead-weight type creep testing frames were used for the creep and stress-rupture tests. These machines are calibrated to operate well within the accuracy requirements of ASTM method E139-66T.

Specimens similar to those used for tension tests were used for the creep and stress-rupture studies. A platinum strip "slide rule" extensometer is attached for measuring creep strain and three Chromel-Alumel thermocouples are attached to the gage section for temperature measurements. Extensometer measurements were made visually through windows in the furnace by means of a filar micrometer microscope in which the smallest division equals 0.00005 inch.

The furnace was of conventional Chromel A wire-wound design with taps along the side to allow for correcting small temperature differences. Furnace temperature was maintained to within ± 2 F by Foxboro controllers in response to signals from the centrally located thermocouple. The temperature of a specimen under test was stabilized for at least 1/2 hour prior to loading.

For each temperature condition creep and stress-rupture data were obtained to 100 and 1000 hours using as many specimens as necessary to obtain precise information. The percent creep deformation obtained was dependent on the material under test. In most instances stress-time curves were defined for 0.2 and 0.5 percent elongation.

Stress Corrosion

Seven specimens of each alloy were tested for susceptibility to stress-corrosion cracking by alternate immersion in 3-1/2 percent sodium chloride solution at room temperature.

Specimens were prepared for testing by degreasing with acetone. Where a surface film remained from heat treating, it was abraded off one side and the adjacent long edge of five of the specimens, and left intact on the other two.

Each specimen was placed in a four-point loading fixture and deflected to a stress corresponding to 80 percent of the tensile yield strength of the particular material. The specimen was electrically insulated from the fixture by means of glass or sapphire rods. Deflection for a given maximum fiber stress was calculated by the following expression:

$$y = \frac{\sigma(3l^2 - 4a^2)}{12dE}$$

where

y = deflection

σ = maximum fiber stress

l = distance between outer load points

a = distance between outer and inner load points

d = specimen thickness

E = modulus of specimen material.

Each stressed specimen was suspended on an alternate immersion unit. This unit alternately immersed specimens in the 3.5 percent sodium chloride solution for ten minutes and held them above the solution to dry for 50 minutes. Tests were continued to the first sign of cracking or for 1000 hours, whichever occurred first.

Specimens were given frequent low-power microscopic examinations to detect cracks. At the first sign of cracking the specimen was removed. At the conclusion of the test, selected samples were sectioned and examined metallographically for any indication of cracking. Representative samples in which cracks were found were also given a metallographic examination to establish the type and extent of the cracks.

Thermal Expansion

Linear-thermal-expansion measurements were performed in a recording dilatometer with specimens protected by a vacuum of about 2×10^{-5} mm of mercury. In this apparatus a sheet-type specimen is supported between two graphite structures inside a tantalum-tube heater element. On heating, the differential movement of the two structures caused by specimen expansion results in the displacement of the core of a linear-variable differential transformer. The output of the transformer is recorded continuously as a function of specimen temperature. The entire assembly is enclosed in a vacuum chamber.

The furnace is controlled to heat at the desired rate, usually 5 F per minute. Errors associated with measurements in this apparatus are estimated not to exceed ± 2 percent. This is based on calibration with materials of known thermal-expansion characteristics.

Fatigue

Fatigue tests were conducted using MTS electrohydraulic-servocontrolled testing machines. The frequency of cycling of these machines is variable to beyond 2,000 cpm depending on specimen rigidity. These machines operate with closed-loop deflection, strain or load control. Under load control used in this program, cyclic loads were automatically maintained (regardless of the required amount of ram travel) by means of load-cell feedback signals. The calibration and alignment of each machine are checked periodically. In each case, the dynamic load-control accuracy is better than ± 3 percent of the test load.

For elevated temperature studies, an induction heating coil controlled by a Lepel Induction Heater was used. A thermocouple placed on the center of the specimen controlled temperature to ± 5 degrees.

After machining and heat treating (when required), the edges of all sheet and plate specimens were polished according to Battelle-Columbus' standard practice prior to testing. The unnotched specimens were held against a rotating drum covered with emery paper and polished using a kerosene lubricant. Successively finer grits of emery paper were used, as required, to produce a surface

of about 10 RMS. Unnotched round specimens were polished in the Battelle-Columbus polishing apparatus. This machine utilizes a rotating belt sander driven rectilinearly along the specimen test section while the specimen is being rotated. The belt speed and specimen speed are adjusted so that polishing marks on the specimen are in the longitudinal direction. The surface finish is about the same as that on the flat specimens. The notched flat specimens were held in a fixture and polished with a slurry of oil and alundum grit applied liberally to a rotating wire. Notched round specimens are polished in the same manner, except that the specimen is rotated.

A shadowgraph optical comparator was used for measuring the test sections of all polished specimens and for inspection of the root radius in the case of the notched specimens.

The stress ratio for all specimens was $R = 0.1$. Stresses for notched ($K_t = 3.0$) and unnotched specimens were selected so that S-N curves were defined between 10^3 and 10^7 cycles using approximately 10 specimens for each set of fatigue conditions.

Fracture Toughness

Two types of fracture toughness tests were used. For heavy section materials, the chevron-notched, slow bend test specimen of ASTM Method E-399-72 was selected. For thinner section sheet materials, center through-cracked tension panels were used as test specimens. All specimens were precracked in fatigue and subsequently fractured in a servocontrolled electrohydraulic testing system of appropriate load capacity.

The slow-bend type specimens were precracked and tested under 3-point loading. The pop-in load for materials susceptible to brittle fracture was determined from the load-compliance curve. When pop-in was not detectable, the curves were analyzed using the 5 percent secant offset method of the ASTM procedure.

The thin sheet center through-crack tension panels were initially saw-cut and then precracked in constant amplitude fatigue loading. In order to maintain a flat fatigue crack and not plastically strain the uncracked section, the maximum stresses were adjusted to keep the applied stress-intensity factor less than one-third or one-quarter of that anticipated at fracture. This usually involved stepping down the stresses as the cracking proceeded. The crack was extended to approximately one-quarter of the panel width. Buckling guides were attached and a clip-type compliance gage was mounted in the central notch. The panels were fractured in a rising load test at a stress rate in the range

$$.002 E < \dot{S} < .005 E \text{ ksi/min}$$

which corresponds nominally to the gross strain rate of standard tensile testing.

APPENDIX II
SPECIMEN DRAWINGS

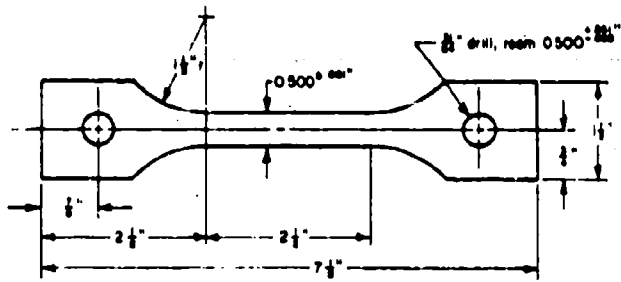


FIGURE 60. SHEET AND THIN-PLATE TENSILE SPECIMEN


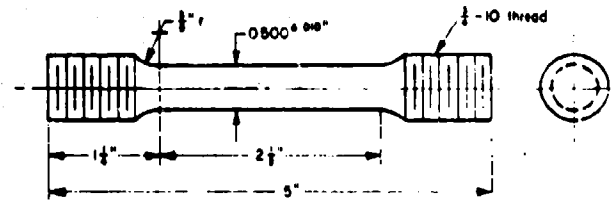


FIGURE 61. ROUND TENSILE SPECIMEN

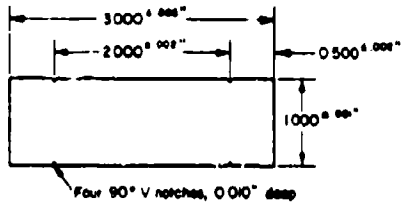

- Notes 1 Ends must be flat and parallel to within 0.0002".
 2 Surface must be free from nicks and scratches

FIGURE 62. SHEET COMPRESSION SPECIMEN

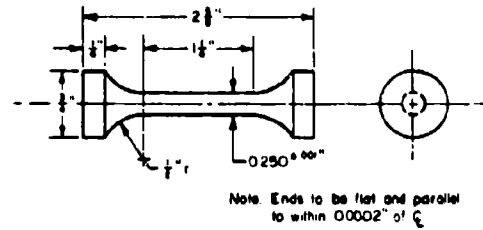


FIGURE 63. ROUND COMPRESSION SPECIMEN

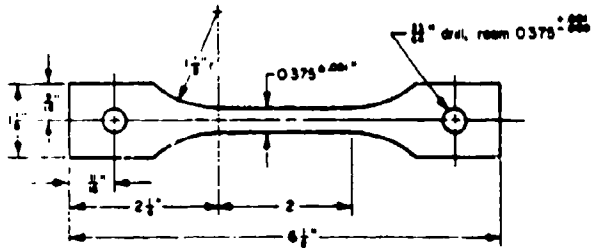


FIGURE 64. SHEET CREEP - AND STRESS- RUPTURE SPECIMEN

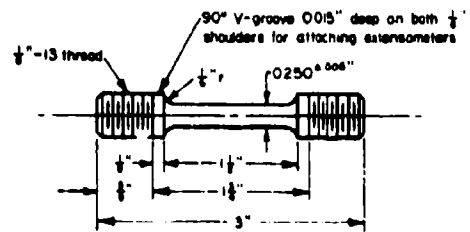


FIGURE 65. ROUND CREEP - AND STRESS- RUPTURE SPECIMEN

A-1363

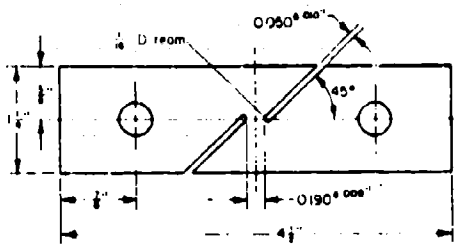


FIGURE 66. SHEET SHEAR TEST SPECIMEN




FIGURE 67. PIN SHEAR SPECIMEN

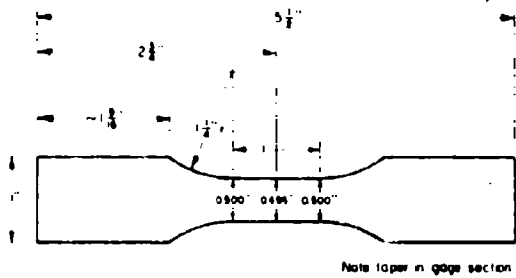


FIGURE 68. UNNOTCHED SHEET FATIGUE SPECIMEN

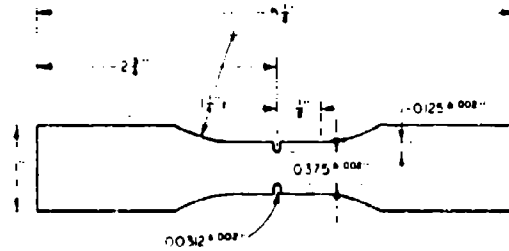


FIGURE 69. NOTCHED SHEET FATIGUE SPECIMEN

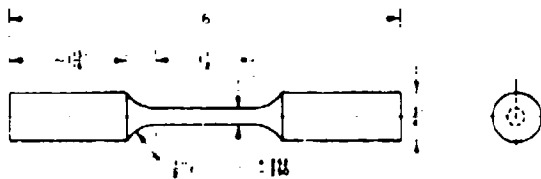


FIGURE 70. UNNOTCHED ROUND FATIGUE SPECIMEN

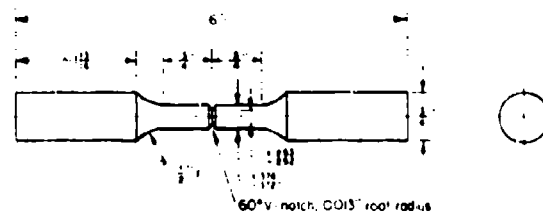


FIGURE 71. NOTCHED ROUND FATIGUE SPECIMEN

A-1226

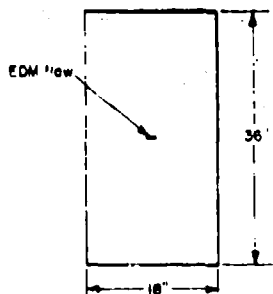


FIGURE 72. SHEET FRACTURE TOUGHNESS SPECIMEN

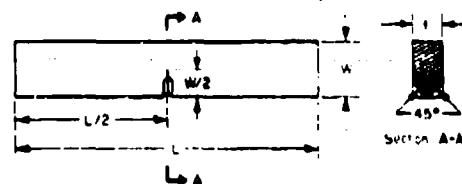


FIGURE 73. SLOW BEND FRACTURE TOUGHNESS SPECIMEN

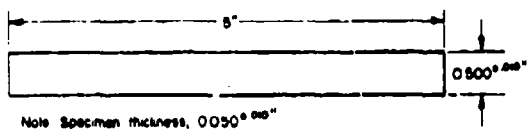


FIGURE 74. STRESS-CORROSION SPECIMEN

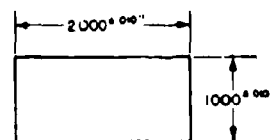


FIGURE 75. THERMAL-EXPANSION SPECIMEN

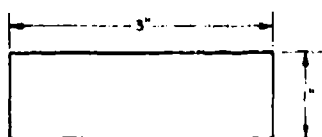


FIGURE 76. SHEET BEND SPECIMEN

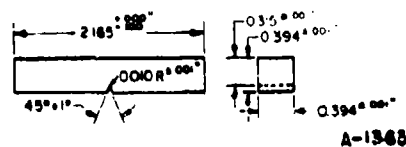


FIGURE 77. NOTCHED IMPACT SPECIMEN

APPENDIX III

DATA SHEETS

X2048-TB51 Aluminum Alloy

X2048-TB51 Aluminum Alloy Data (a)

Thickness: 3-inch plate

Material Description

Alloy X2048-TB51 is a recent development of the Reynolds Metals Company. The development aim was a thick section alloy with high toughness and stability at moderate temperatures. The goal was to achieve the strength, fatigue resistance, corrosion resistance, and thermal stability of 2024-TB51 or 2124-TB51 and the toughness of 2219.

The material used for this evaluation was 3-inch plate produced within the following composition limits:

Copper	2.8 to 3.8
Manganese	0.20 to 0.60
Magnesium	1.2 to 1.6
Zinc	0.25 max
Titanium	0.10 max
Silicon	0.15 max
Iron	0.70 max
Others total	0.15 max
Aluminum	Balance

Processing and Heat Treating

The specimens were tested in the as-received -TB51 temper.

Properties	Temperature, F		500
	250	350	
<u>Tension</u>			
TUS (longitudinal), ksi	66.3	51.4	34.0
TUS (transverse), ksi	67.4	50.3	33.4
TUS (short transverse), ksi	67.1	U	U
TYS (longitudinal), ksi	60.4	49.1	31.7
TYS (transverse), ksi	60.9	56.3	31.6
TYS (short transverse), ksi	58.9	U	U
e (longitudinal), percent in 2 in.	8.3	12.7	9.5
e (transverse), percent in 2 in.	7.2	12.7	8.2
e (short transverse), percent in 2 in.	6.3	U	U
MA (longitudinal), percent	15.7	31.6	23.4
MA (transverse), percent	11.7	27.7	15.0
RA (short transverse), percent	9.4	U	U
E (longitudinal), 10 ⁶ psi	10.2	9.9	8.3
E (transverse), 10 ⁶ psi	10.5	9.8	7.7
E (short transverse), 10 ⁶ psi	11.1	U	U
<u>Compression</u>			
CYS (longitudinal), ksi	60.9	56.7	35.2
CYS (transverse), ksi	60.6	56.0	32.9
E _c (longitudinal), 10 ⁶ psi	11.3	10.2	9.4
E _c (transverse), 10 ⁶ psi	11.1	10.3	9.6
<u>Shear (b)</u>			
SUS (longitudinal), ksi	39.3	(c)	U
SUS (transverse), ksi	39.2	U	U
<u>Lapact (d)</u>			
V-notch Charpy, ft. lb. (longitudinal)	7.6	U	U
(transverse)	4.5	U	U
<u>Fracture Toughness (e)</u>			
K _{IC} , crack direction II, ksi √in.	32.0	U	U
K _{IC} , crack direction I, ksi √in.	29.1	U	U

X2048-T851 Aluminum Alloy
(continued)

Properties	RT	250	350	500
Axial Fatigue (Longitudinal) (1)				
Unnotched, R = 0.1				
10 ⁷ cycles, ksi	63	63		U
10 ⁶ cycles, ksi	38	37	35	U
10 ⁵ cycles, ksi	32	28	25	U
Notched, K _t = 3.0, R = 0.1				
10 ⁷ cycles, ksi	54	54	50	U
10 ⁶ cycles, ksi	22	21	19	U
10 ⁵ cycles, ksi	16	14	12	U
(Creep (Longitudinal))				
0.2% plastic deformation, 100 hr, ksi	NA (c)	44	35	8.5
0.2% plastic deformation, 1000 hr, ksi	NA	41	19	4.5
Stress-Rupture (Longitudinal)				
Rupture, 100 hr, ksi	NA	50	39	13
Rupture, 1000 hr, ksi	NA	47	32	8.5
Stress Corrosion (8)				
80% TWS, 1000 hr maximum				no cracks
Coefficient of Thermal Expansion				U
Density				
				.0994 lb/in ³

- (a) Values are average of triplicate tests conducted at Battelle under the subject contract unless otherwise indicated. Fatigue, creep, and stress-rupture values are from curves generated using the results of a greater number of tests.
- (b) Double-shear pin-type specimen; average of 4 tests in each direction.
- (c) U, unavailable; NA, not applicable.
- (d) Values are average of 6 tests in each direction.
- (e) Values are average of 6 slow-bend type tests in each direction. Specimen size was 1.000-inch thick by 2.000 inches wide with a span of 8 inches. (Higher K_t values may be achieved with larger specimens. Reference J. G. Kaufman, "Notes for E-24-01 Meeting", held at Battelle's Columbus Laboratories on October 4, 1972.
- (1) "R" represents the algebraic ratio of minimum stress to maximum stress in one cycle; that is, $R = S_{min}/S_{max}$. "K_t" represents the Neuber-Peterson theoretical stress concentration factor.
- (8) Room-temperature three-point bend test. Alternate immersion in 3-1/2% NaCl.

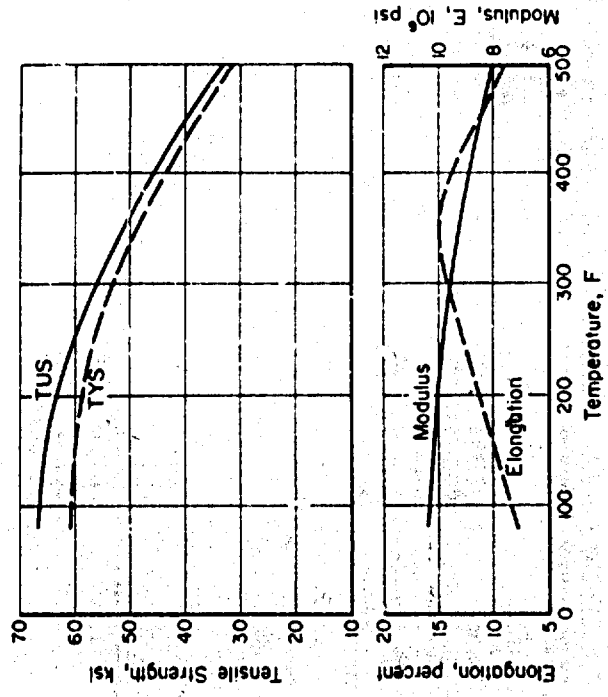


FIGURE 1. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF X2048-T851 PLATE

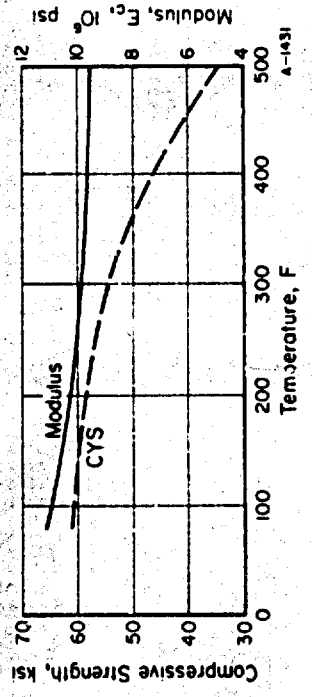


FIGURE 2. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF X2048-T851 PLATE

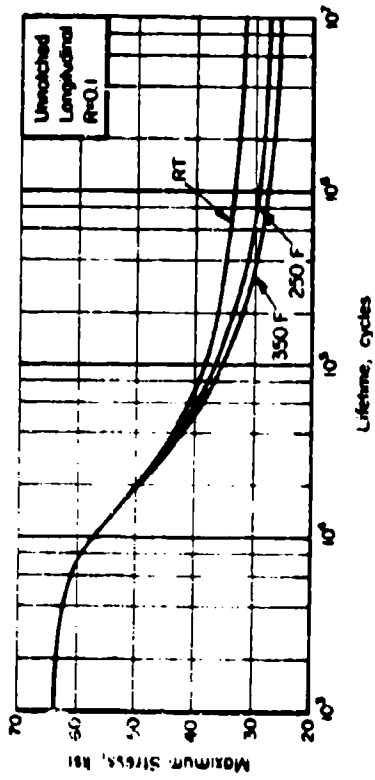


FIGURE 3. AXIAL LOAD FATIGUE BEHAVIOR OF UNNOTCHED K2048-1851 PLATE

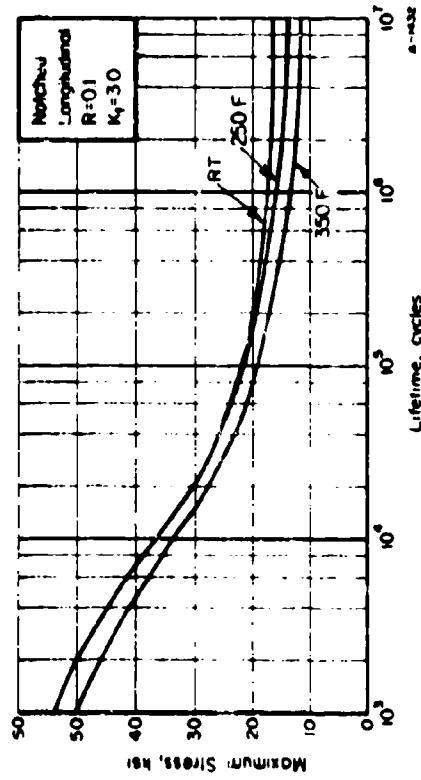


FIGURE 4. AXIAL LOAD FATIGUE BEHAVIOR OF NOTCHED ($K_t = 3.0$) K2048-1851 PLATE

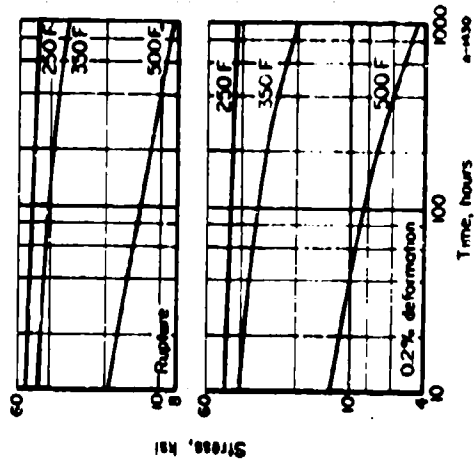


FIGURE 5. STRESS-RUPTURE AND PLASTIC DEFORMATION CURVES FOR K2048-1851 PLATE (LONGITUDINAL)

7050-T73651 Aluminum Alloy Data (a)

7050-T73651 Aluminum Alloy

Thickness: 1-inch plate

Material Description

Alloy 7050 is an Al-Zn-Mg-Cu alloy developed by the Alcoa Research Laboratories supported by the Naval Air Systems Command and the Air Force Materials Laboratory. When heat treated and aged to the T7 temper, thick 7050 plate and hand forgings exhibit strengths equal to or exceeding those of 7079-T6XN products combined with improved fracture toughness and high resistance to exfoliation and stress-corrosion cracking. The alloy differs from conventional 70XX series aluminum alloys in that zirconium is added and chromium and manganese are restricted in order to minimize punch sensitivity.

The material used in this evaluation was 1-inch plate from Heat S-16420 produced within the following composition limits:

Copper	2.0 to 2.8
Iron	0.15 max
Silicon	0.12 max
Manganese	0.10 max
Magnesium	1.9 to 2.6
Zinc	5.7 to 6.7
Chromium	0.05 max
Titanium	0.06 max
Aluminum	Balance

Processing and Heat Treatment

Specimens were tested in the as-received -T73651 temper.

Properties	Temperature, F		
	RT	350	500
Tension			
TUS (longitudinal), ksi	82.6	65.0	53.7
TUS (transverse), ksi	81.5	64.5	53.5
TYS (longitudinal), ksi	73.8	64.9	53.9
TYS (transverse), ksi	72.5	64.1	53.3
ϵ (longitudinal), percent in 2 in.	11.7	15.5	16.8
ϵ (transverse), percent in 2 in.	10.5	13.3	14.7
RA (longitudinal), percent	30.2	48.1	58.1
RA (transverse), percent	34.5	48.7	57.8
E (longitudinal), 10^6 psi	10.3	9.4	8.4
E (transverse), 10^6 psi	11.5	9.7	8.7
Compression			
CYS (longitudinal), ksi	73.0	64.3	53.7
CYS (transverse), ksi	75.3	66.1	55.1
ϵ_c (longitudinal), 10^6 psi	10.8	9.5	9.1
ϵ_c (transverse), 10^6 psi	11.0	10.0	9.4
Shear (b)			
SYS (longitudinal), ksi	48.7	U (c)	U
SYS (transverse), ksi	47.9	U	U
Impact (d)			
V-notch Charpy, ft.-lb. (longitudinal)	34.7	U	U
(transverse)	5.7	U	U
Fracture Toughness (e)			
K_{Ic} I-I, ksi $\sqrt{\text{in.}}$	27.7	U	U
K_{Ic} L-I, ksi $\sqrt{\text{in.}}$	30.9	U	U
Axial Fatigue (transverse) (f)			
Unnotched, R = 0.1			
10 ⁷ cycles, ksi	60	56	U
10 ⁸ cycles, ksi	42	34	U
10 ⁹ cycles, ksi	31	20	U
Notched, $K_t = 5.0$, R = 0.1			
10 ⁷ cycles, ksi	44	43	U
10 ⁸ cycles, ksi	19	16	U
10 ⁹ cycles, ksi	12	10	U

7050-T 16S1 Aluminum Alloy Data
(continued)

Properties	Temperature, F		
	RT	250	500
Creep (transverse)			
0.2% plastic deformation, 100 hr, ksi	NA (c)	49	21
0.2% plastic deformation, 1000 hr, ksi	NA	35	13.5
Stress-Rupture (transverse)			
Rupture, 100 hr, ksi	NA	53	26
Rupture, 1000 hr, ksi	NA	47	17
Stress Corrosion (a)			
80% TYS, 1000 hr maximum	no cracks		
Coefficient of Thermal Expansion			
12.6 x 10 ⁻⁶ in/in/F (68 to 212 F)			
Density			
0.102 lb/in ³			

- (a) Values are average of triplicate tests conducted at Battelle under the subject contract unless otherwise indicated. Fatigue, creep, and stress-rupture values are from curves generated using the results of a greater number of tests.
- (b) Double-shear pin-type specimen; average of 4 tests in each direction.
- (c) T, unavailable; NA, not applicable.
- (d) Average of 6 tests in each direction.
- (e) Values are average of 6 six-head type tests in each direction. Specimen size was 1.000-inch thick by 2.000 inches wide with a span of 8 inches.
- (f) "R" represents the algebraic ratio of minimum stress to maximum stress in one cycle; that is, $R = S_{min}/S_{max}$. "K_c" represents the Miner-Petersen theoretical stress concentration factor.
- (g) Room-temperature three-point bend test. Alternate immersion in 3-1/2% NaCl.

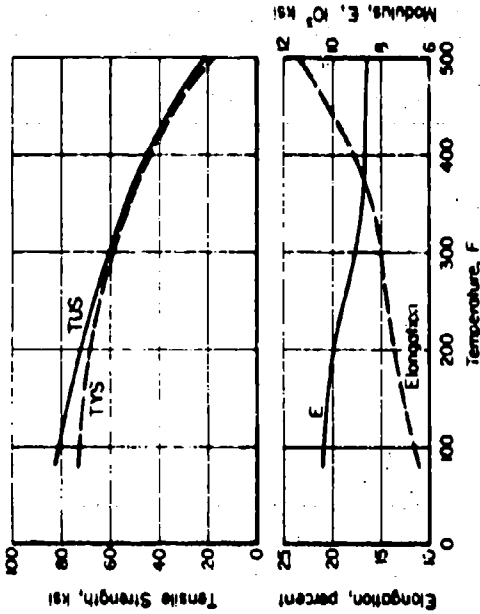


FIGURE 1. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF 7050-T16S1 ALUMINUM ALLOY PLATE

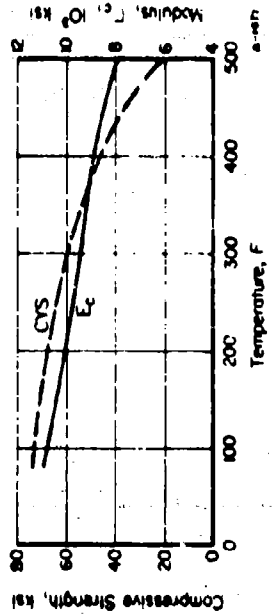


FIGURE 2. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF 7050-T16S1 ALUMINUM ALLOY PLATE

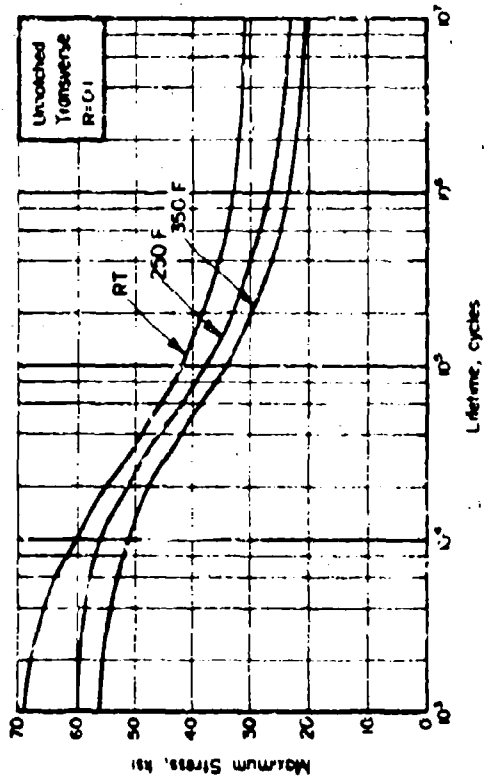


FIGURE 3. AXIAL LOW FATIGUE BEHAVIOR OF UNNOTCHED 7050-T7351 ALUMINUM PLATE (TRANSVERSE)

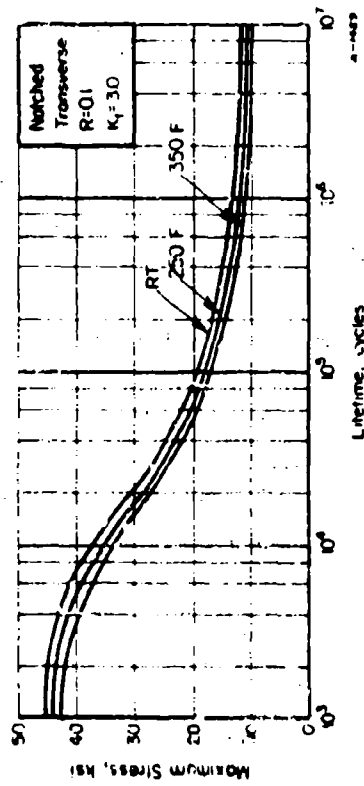


FIGURE 4. AXIAL LOW FATIGUE BEHAVIOR OF NOTCHED 7050-T7351 ALUMINUM PLATE (TRANSVERSE)

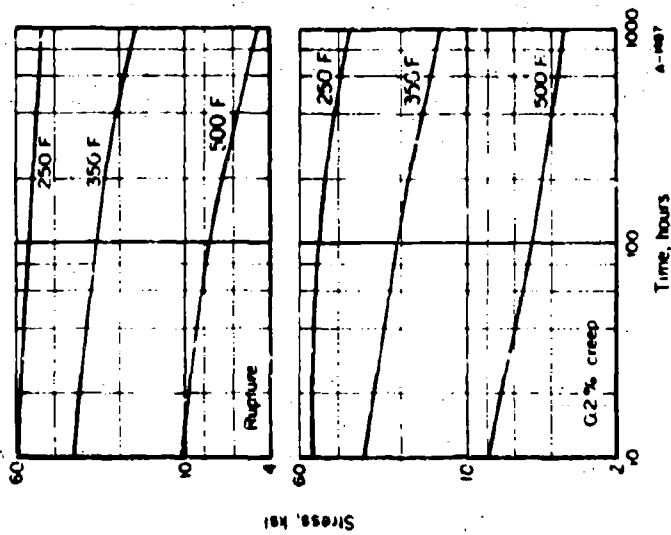


FIGURE 5. STRESS-RUPTURE AND PLASTIC DEFORMATION CURVES FOR 7050-T7351 ALUMINUM ALLOY PLATE (TRANSVERSE)

21-6-9 Stainless Steel Alloy

21-6-9 Stainless Steel Alloy

Material Description

Alloy 21-6-9 is a recent development of the Armco Steel Corporation. It is an austenitic stainless steel, combining high yield strength with good corrosion resistance. The room temperature yield strength of 21-6-9 is superior to Types 304, 321, and 347. It has good elevated temperature properties and retains high strength and toughness at subzero temperatures.

Armco 21-6-9 stainless steel is available in standard finishes in annealed or high tensile temper sheet and strip as well as in bar, wire, forging billets, and plate.

The material used in this evaluation was an 0.072-inch thick sheet produced within the following composition limits:

Carbon	0.08 max
Manganese	5.00 - 10.00
Phosphorus	0.060 max
Sulfur	0.030 max
Silicon	1.00 max
Chromium	19.00 - 21.50
Nickel	5.50 - 7.50
Niobium	0.15 - 0.40
Iron	Balance

Processing and Heat Treating

The alloy was evaluated in the as-received annealed condition.

Properties	RT	400	700	900
<u>Tension</u>				
TUS (longitudinal), ksi	113.0	88.1	83.7	76.1
TUS (transverse), ksi	113.3	88.4	83.2	76.5
TUS (longitudinal), ksi	94.8	42.5	35.9	33.0
TUS (transverse), ksi	65.7	42.7	35.4	33.2
E (longitudinal), percent in 2 in.	55.0	43.5	45.6	41.9
E (transverse), percent in 2 in.	50.0	42.0	41.8	41.3
E (longitudinal), 10 ⁶ psi	26.6	21.1	21.7	19.2
E (transverse), 10 ⁶ psi	28.4	19.9	18.4	16.3
<u>Compression</u>				
CYS (longitudinal), ksi	67.2	45.1	40.5	34.7
CYS (transverse), ksi	66.5	46.3	37.9	34.1
E _c (longitudinal), 10 ⁶ psi	28.5	26.7	25.8	25.1
E _c (transverse), 10 ⁶ psi	29.0	28.8	26.5	25.7
<u>Shear (b)</u>				
SUS (longitudinal), ksi	102.3	(c)	(c)	(c)
SUS (transverse), ksi	102.8	(c)	(c)	(c)
<u>Bend (d)</u>				
Minimum Radius	11	(e)	(e)	(e)
<u>Fracture Toughness</u>				
K _{IC} , T-L, ksi/in.	(e)	(e)	(e)	(e)
<u>Axial Fatigue (transverse) (f)</u>				
Unnotched, R = 0.1	106	90	80	(g)
10 ⁷ cycles, ksi	92	82	74	(g)
10 ⁸ cycles, ksi	86	75	68	(g)

21-6-9 Stainless Steel Data
(continued)

Properties	Temperature, F			
	RI	400	700	900
<u>Axial Fatigue (transverse) (continued)</u>				
Notched, $K_t = 3.0$, $R = 0.1$				
10 ⁷ cycles, ksi	80	75	75	71
10 ⁶ cycles, ksi	61	44	44	41
10 ⁵ cycles, ksi	46	36	36	31
<u>Creep (transverse)</u>				
0.2% plastic deformation, 100 hr, ksi	NA (C)	50	33	31
0.2% plastic deformation, 1000 hr, ksi	NA	35	32	30
<u>Stress Rupture (transverse)</u>				
Rupture, 100 hr, ksi	NA	85	83	72
Rupture, 1000 hr, ksi	NA	82	82	65
<u>Stress Corrosion (C)</u>				
80 T.S., 1000 hr max/min				no cracks
<u>Coefficient of Thermal Expansion</u>				
$10^{-6} \times 10^{-3} \text{ in/in/F (8-1100 F)}$				

Density

7.283 lb./in³

- (a) Values are average of triplicate tests conducted at battelle under the subject contract unless otherwise indicated. Fatigue, creep, and stress-rupture values are from curves generated using the results of a greater number of tests.
- (b) Sheet-shear type specimen; average of 4 tests in each direction.
- (c) T, unavailable; NA, not applicable.
- (d) Specimens tested from RI to 900 F. No cracks.
- (e) Transverse specimens were full sheet thickness by 1/8 inches wide by 3/8 inches long with an Ege fillet in the center. The net section yield strength was greater than the tensile yield strength of the material; therefore, the K values obtained are considered NOT VALID.
- (f) σ_R represents the algebraic ratio of minimum stress to maximum stress in one cycle; that is $R = \frac{\sigma_{min}}{\sigma_{max}}$. " N_f " represents the Neuber-Peterson theoretical stress concentration factor.
- (g) Room-temperature intermittent bend test. Alternate immersion in 3-1/2% NaCl.

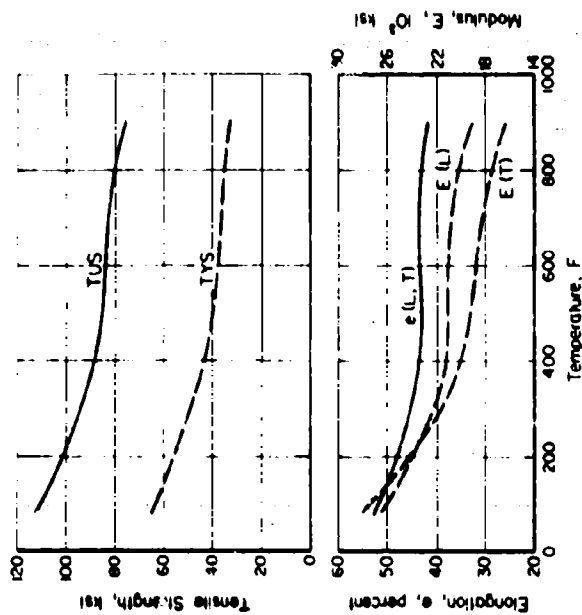


FIGURE 1. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF ANNEALED 21-6-9 STAINLESS STEEL SHEET

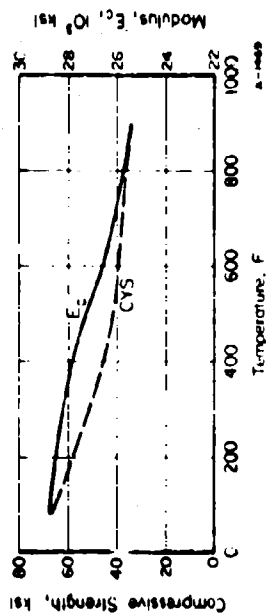


FIGURE 2. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF ANNEALED 21-6-9 STAINLESS STEEL SHEET

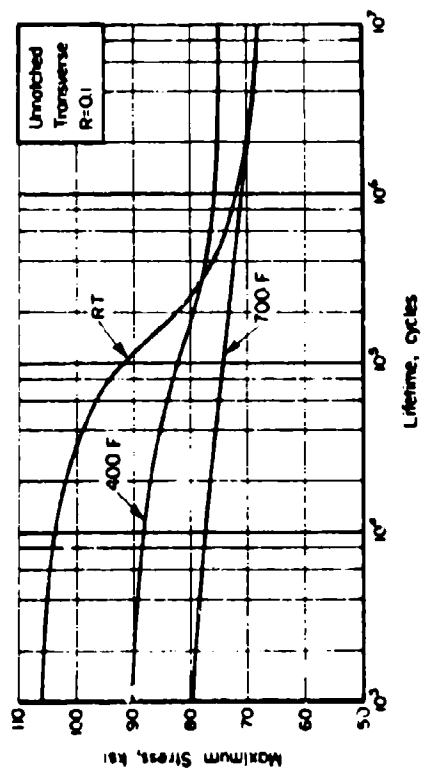


FIGURE 3. AXIAL LOAD FATIGUE BEHAVIOR OF UNNOTCHED ANNEALED 21-6-9 STAINLESS STEEL SHEET

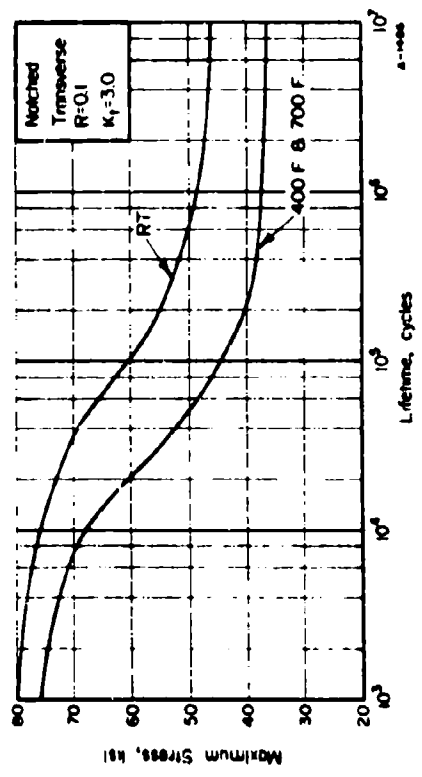


FIGURE 4. AXIAL LOAD FATIGUE BEHAVIOR OF NOTCHED ANNEALED 21-6-9 STAINLESS STEEL SHEET

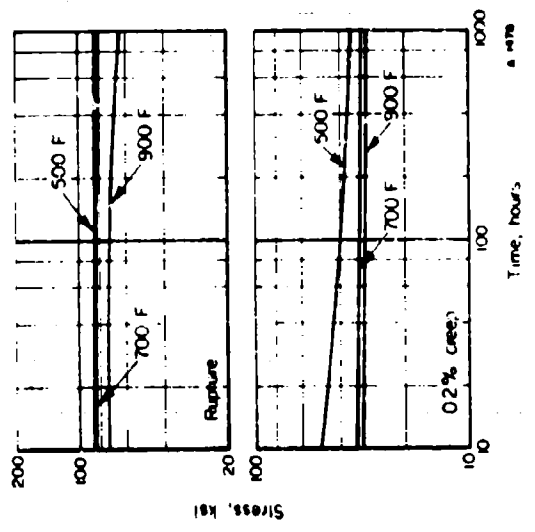


FIGURE 5. STRESS-RUPTURE TIME AND PLASTIC DEFORMATION CURVES FOR ANNEALED 21-6-9 STAINLESS STEEL SHEET

II-890-8V-2Fe-2Al Alloy (1)

II-890-8V-2Fe-2Al Alloy

Condition: Solution treated and aged 900 F
 Thickness: 0.040-inch sheet

Material Description

The 890-8V-2Fe-2Al beta titanium alloy is a recent development of TIMET. The alloy was selected for full-scale evaluation after confirming (by arc process) that it could be melted by the conventional consumable electrode vacuum arc process. It shows producibility and property characteristics that make it suitable for a variety of airframe applications. A variety of heat treatments are available to allow the designer to take advantage of its individual properties or its generally good overall properties. Its short aging times and low density make it particularly desirable for some applications.

The material used in this evaluation was from TIMET Heat K-5055 and was analyzed as follows:

% Vanadium	8.0
Vanadium	8.2
Iron	2.0
Aluminum	3.0
Aluminum	0.16
Oxygen	0.011
Nitrogen	
Titanium	Balance

Processing and Heat Treating

The material was received in the solution treated condition. Specimens were aged at 900 F for 6 hours. This condition is called the high strength, fully-aged condition.

Properties	Tensile, F		
	RY	490	600
TUS (longitudinal), ksi	160.3	148.7	155.0
TUS (transverse), ksi	172.7	155.3	152.3
TYS (longitudinal), ksi	144.7	123.3	117.7
TYS (transverse), ksi	158.0	133.3	124.0
e (longitudinal), percent in 2 in.	11.2	9.0	7.3
e (transverse), percent in 2 in.	9.5	6.8	6.7
E (longitudinal), 10 ³ psi	13.6	13.3	12.4
E (transverse), 10 ³ psi	14.9	14.1	13.2

Compression

CYS (longitudinal), ksi	177.7	140.7	136.7
CYS (transverse), ksi	191.7	163.7	151.7
E _c (longitudinal), 10 ³ psi	15.9	14.5	14.2
E _c (transverse), 10 ³ psi	16.9	15.1	14.6

Shear (b)

SUS (longitudinal), ksi	170.5	(c)	U
SUS (transverse), ksi	154.6	U	U

Fracture Toughness (d)

K _{Ic} , T-L, ksi/√in.	44	U	U
---------------------------------	----	---	---

Axial Fatigue (Transverse) (e)

Unnotched, R = 0.1			
10 ⁷ cycles, ksi	118	138	130
10 ⁶ cycles, ksi	74	74	67
10 ⁵ cycles, ksi	63	63	60
Notched, K _t = 3.0, R = 0.1			
10 ⁷ cycles, ksi	104	109	98
10 ⁶ cycles, ksi	30	31	26
10 ⁵ cycles, ksi	22	22	20

11-870-88-2 (Fe-3Al Alloy Data
(continued))

Properties	Temperature, F	
	551	700
Creep (Transverse)		
0.2% plastic deformation, 100 hr, ksi	MA	70
0.2% plastic deformation, 1000 hr, ksi	MA	40
Stress Rupture (Transverse)		
Rupture 100 hr, ksi	MA	149
Rupture 1000 hr, ksi	MA	147
Stress Corrosion (f)		
60 TYS, 1000 hr maximum	no cracks	

Coefficient of Thermal Expansion

5.0×10^{-6} in./in./F (RT to 800 F)

Density

0.175 in/in.

- (a) Values are average of triplicate tests conducted at Battelle under the subject contract unless otherwise indicated. Fatigue, creep, and stress-rupture values are from curves generated using the results of a greater number of tests.
- (b) Sheet-shear type specimen; average of 5 tests in each direction.
- (c) U, unavailable; MA, not applicable.
- (d) Transverse specimens were full sheet thickness by 18 inches wide by 36 inches long with an LPM flaw in the center.
- (e) "mg" represents the algebraic ratio of minimum stress to maximum stress in one cycle; that is $R = S_{min}/S_{max}$. "L" represents the Neuber-Peterson theoretical stress concentration factor.
- (f) Room-temperature three-point bend test. Alternate immersion in 3-1/2% NaCl.

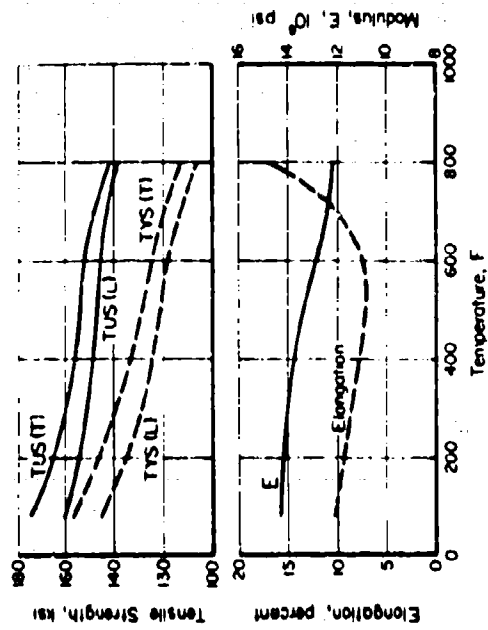


FIGURE 1. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF SOLUTION TREATED AND AGED 11-870-88-2(Fe-3Al) ALLOY SHEET

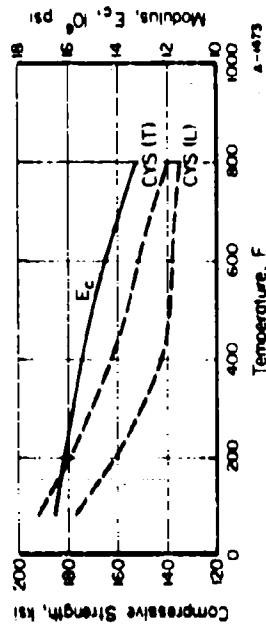


FIGURE 2. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF SOLUTION TREATED AND AGED 11-870-88-2(Fe-3Al) ALLOY SHEET

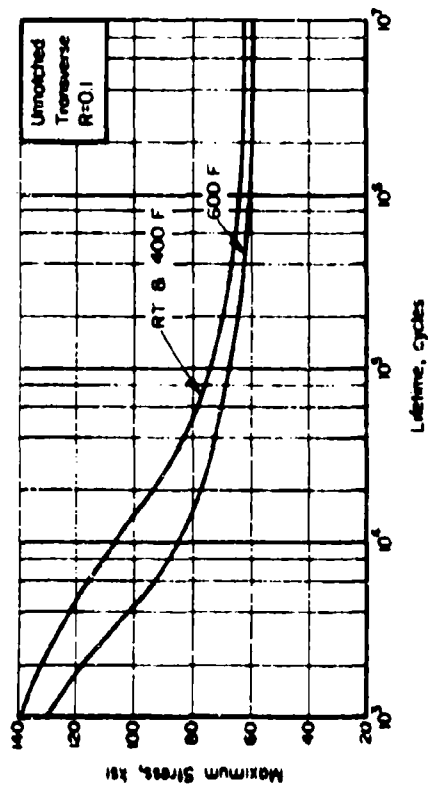


FIGURE 3. AXIAL LOAD FATIGUE BEHAVIOR OF UNNOTCHED SOLUTION TREATED AND AGED Ti-8Nb-8V-2Fe-3Al ALLOY SHEET

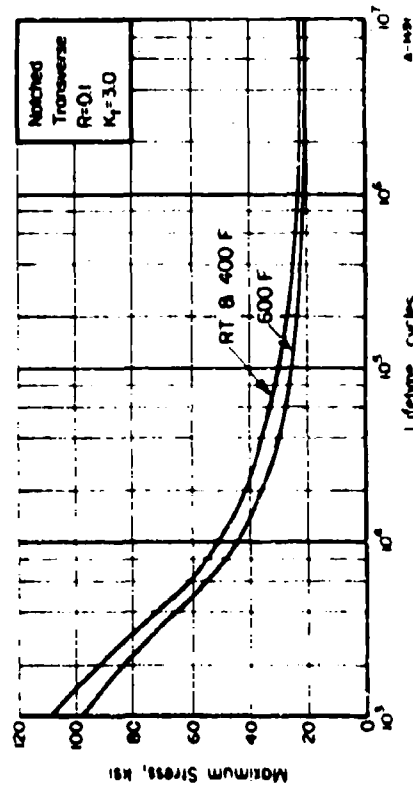


FIGURE 4. AXIAL LOAD FATIGUE BEHAVIOR OF NOTCHED SOLUTION TREATED AND AGED Ti-8Nb-8V-2Fe-3Al ALLOY SHEET

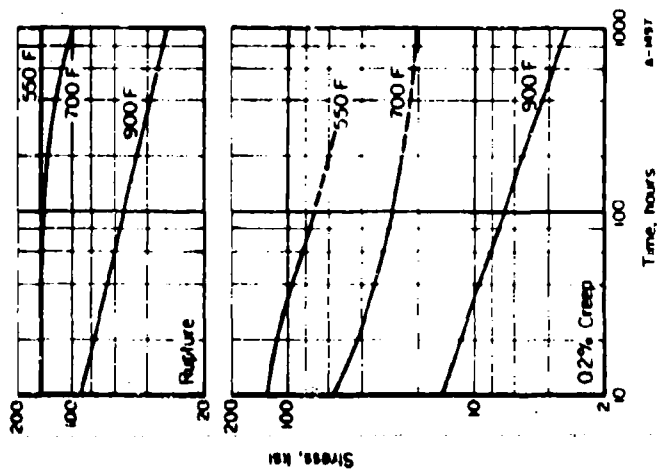


FIGURE 5. STRESS-STRAIN AND PLASTIC DEFORMATION CURVES FOR SOLUTION TREATED AND AGED Ti-8Nb-8V-2Fe-3Al ALLOY

Ti-6Al-2Zr-2Sn-2Mo-2Cr Alloy

Ti-6Al-2Zr-2Sn-2Mo-2Cr Alloy DATA (a)

Material Description

This alloy is a recent development of RMI Company. It is an alpha-beta type alloy designed for deep hardenability. Preliminary information shows the material to have low density, high modulus, high toughness, and good producibility. Strength retention to 800 F is good.

The material used for this evaluation was a 1 1/2-inch thick plate from RMI ingot number 890189 which had the following chemistry:

Al	5.8
Sn	2.1
Zr	1.8
Mo	2.0
Cr	1.9
Si	0.21
Fe	0.06
C	0.02
N ₂	0.010
O ₂	0.012

Additional information on this alloy is available on work performed by RMI Company under Wright Field Air Force Contract F33615-72-C-1152.

Processing and Heat Treatings

The plate product evaluated was alpha beta processed to develop a refined microstructure. The plate was received in the solution-treated condition (1740 F, 1 hour, Air Cooled) condition. Specimens were then aged at 1000 F for 8 hours. It should be noted that heavier sections require oil or water quench to effectively solution treat the product.

Condition: solution treated and aged
Thickness: 1 1/2 inch plate

Properties	RT	Temperature, F	
		400	600
<u>Tension</u>			
TUS (longitudinal), ksi	168.3	145.3	139.0
TUS (transverse), ksi	168.7	146.0	139.7
TYS (longitudinal), ksi	155.5	116.0	107.0
TYS (transverse), ksi	156.5	119.7	108.7
E (longitudinal), percent in 1 in.	18.0	19.5	21.3
E (transverse), percent in 1 in.	17.7	19.7	21.0
RA (longitudinal), percent	24.8	33.2	34.9
RA (transverse), percent	26.2	33.7	33.3
E (longitudinal), 10 ³ psi	17.9	15.9	15.6
E (transverse), 10 ³ psi	17.8	15.2	16.0
<u>Compression</u>			
CYS (longitudinal), ksi	169.7	128.1	112.0
CYS (transverse), ksi	173.3	129.3	115.0
E _c (longitudinal), 10 ³	18.1	16.7	15.8
E _c (transverse), 10 ³ psi	18.5	16.3	15.6
<u>Shear (b)</u>			
SUS (longitudinal), ksi	108.3	(c)	(c)
SUS (transverse), ksi	106.0	(c)	(c)
<u>Impact (d)</u>			
V-notch Charpy, Ft. lb.			
(longitudinal)	13.9	(c)	(c)
(transverse)	15.3	(c)	(c)
<u>Fracture Toughness (e)</u>			
K _{IC} L-T, ksi in.	85.0	(c)	(c)
K _{IC} T-L, ksi in.	93.0	(c)	(c)
<u>Axial Fatigue (transverse) (f)</u>			
Unnotched, R=0.1			
10 ⁶ cycles, ksi	155	150	134
10 ⁷ cycles, ksi	135	123	115
10 ⁸ cycles, ksi	75	75	75
Notched, R=1.0, R=0.1			
10 ⁶ cycles, ksi	120	122	90
10 ⁷ cycles, ksi	59	55	50
10 ⁸ cycles, ksi	42	37	37

TI-6Al-2Zr-2Sn-2Nb-2Cr ALLOY DATA
(Continued)

Properties	Temperature, F	
	RT	600-800
<u>Creep (transverse)</u> 0.7% plastic deformation, 100 hr., ksi	MA	122
0.7% plastic deformation, 1000 hr., ksi	MA	115
<u>Stress-Rupture (transverse)</u> Rupture, 100 hr., ksi	MA	142
Rupture, 1000 hr., ksi	MA	131
<u>Stress Corrosion (b)</u> 80% TYS, 1500 hr. maximum	no cracks	
<u>Coefficient of Thermal Expansion</u> 5.1×10^{-6} in./in./F (68 to 800 F)		
<u>Density</u> 0.165 lb./in. ³		

(a) Values are average of triplicate tests conducted at Battelle under the subject contract unless otherwise indicated. Fatigue, creep, and stress-rupture values are from curves generated using the results of a greater number of tests.

(b) Double-shear pin-type specimen; average of 4 tests in each direction.

(c) U: unavailable; MA: not applicable.

(d) Values are average of 6 tests in each direction.

(e) These values do not meet the rigorous $A_1 T_1 < 2.5 \left(\frac{R_u}{TYS}\right)$ criteria. However, they are over $2.2 \left(\frac{R_u}{TYS}\right)$ and should be considered good indicative K_{Ic} values.

(f) "R" represents the algebraic ratio of minimum stress to maximum stress in one cycle; that is, $R = S_{min}/S_{max}$. "K_{Ic}" represents the Murber-Peterson theoretical stress concentration factor.

(g) Room-temperature three-point bend test. Alternate immersion in 3-1/2% NaCl.

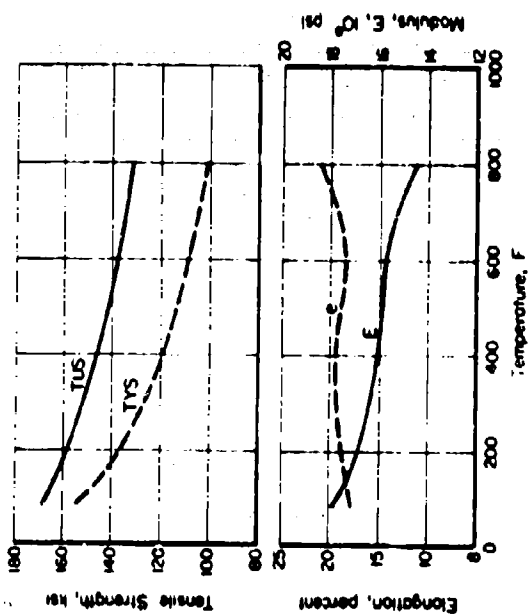


FIGURE 1. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF SOLUTION TREATED AND AGED TI-6Al-2Zr-2Sn-2Nb-2Cr PLATE

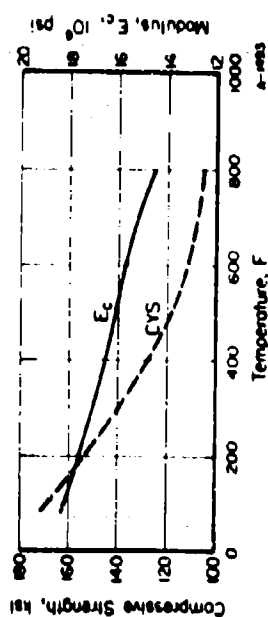


FIGURE 2. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF SOLUTION TREATED AND AGED TI-6Al-2Zr-2Sn-2Nb-2Cr PLATE

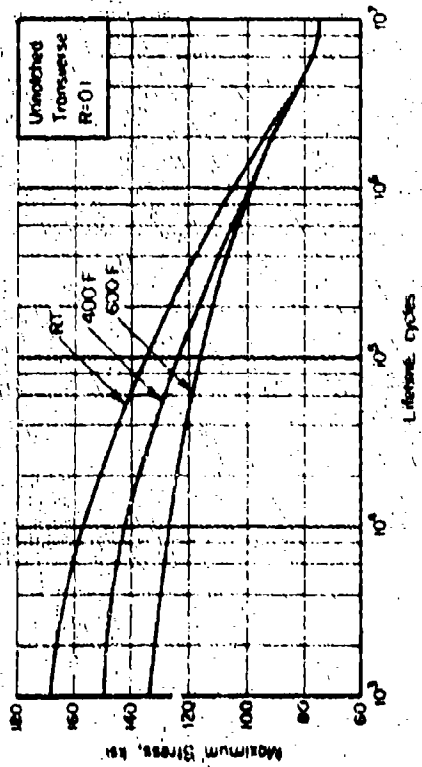


FIGURE 3. AXIAL FATIGUE BEHAVIOR OF UNNOTCHED SOLUTION-TREATED AND AGED Ti-5Al-2Zr-2Sn-2Ta-2Nb PLATE

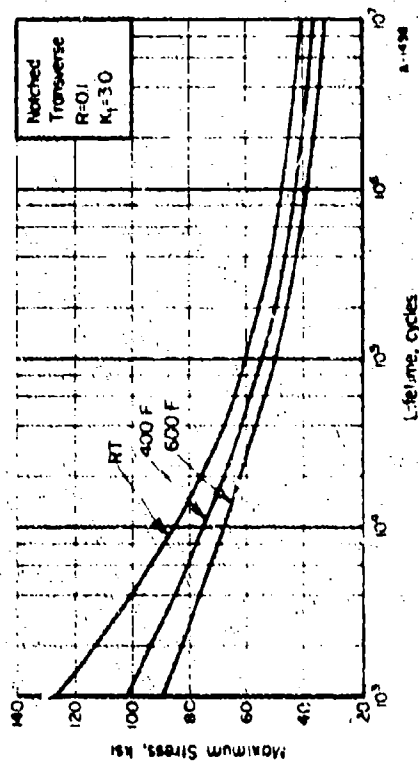


FIGURE 4. AXIAL FATIGUE BEHAVIOR OF NOTCHED (K_t=1.9) SOLUTION-TREATED AND AGED Ti-5Al-2Zr-2Sn-2Ta-2Nb PLATE

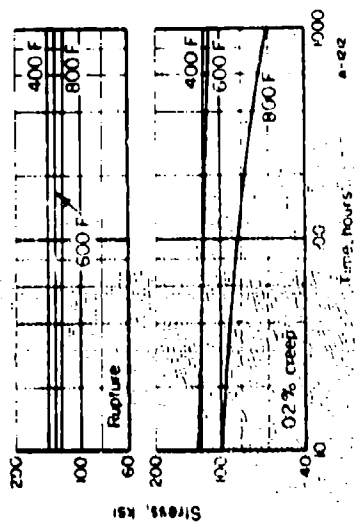


FIGURE 5. STRESS RELAXATION BEHAVIOR OF SOLUTION-TREATED AND AGED Ti-5Al-2Zr-2Sn-2Ta-2Nb PLATE

Ti-6Al-6V-2Sn Isothermal Die Forgings

Material Description

This is a heat-treatable alpha beta type alloy similar in many respects to Ti-6Al-6V, but containing increased content of beta stabilizing elements which provide higher strength potential.

The material used for this evaluation was made by IIT Research Institute under Air Force Contract F33615-67-C-1722. It consisted of structural shapes and nose wheels that were isothermally creep (slow speed) forged from flat preforms machined from conventionally forged Ti-6Al-6V-2Sn alloy billets.

Processing and Heat Treating

The material was received with no heat treatment after forging. Specimens were solution treated at 1650 F for 1/2 hour, water quenched, and aged at 1050 F for 4 hours and air cooled. This treatment was as suggested by IIT Research Institute.

Ti-6Al-6V-2Sn Alloy Data (a)

Condition: Solution treated and aged
thickness: Die forging of varying thickness

Properties	Temperature, F		
	RT	700	900
<u>Tension</u>			
TTS (transverse), ksi	202.5	170.4	158.2
TYS (transverse), ksi	192.9	153.2	131.8
e (transverse), percent in 1 in.	4.7	7.7	8.3
E (transverse), 10 ⁷ psi	16.0	14.7	13.1
<u>Compression</u>			
CYS (transverse), ksi	199.3	175.3	152.9
F _c (transverse), 10 ⁷ psi	18.0	16.1	13.2
<u>Shear</u>			
SYS (longitudinal), ksi	131.6	U ^(c)	U
SYS (transverse), ksi	130.0	U	U
<u>Impact (d)</u>			
V-notch Charpy, ft. lbs. (longitudinal)	11.7	U	U
(transverse)	9.5	U	U
<u>Fracture Toughness (e)</u>			
K _{IC} , L-T, ksi/in.	25.0	U	U
K _{IC} , T-L, ksi/in.	26.7	U	U
<u>Axial Fatigue (transverse) (f)</u>			
Unnotched, R = 0.1			
10 ⁷ cycles, ksi	112	112	112
10 ⁶ cycles, ksi	30	42	50
10 ⁵ cycles, ksi	22	32	42
Notched, K _t = 3.0, R = 0.1			
10 ⁷ cycles, ksi	76	76	76
10 ⁶ cycles, ksi	23	43	53
10 ⁵ cycles, ksi	26	30	32
<u>Creep (transverse)</u>			
0.2 plastic deformation, 100 hr., ksi	NA ^(c)	NA	NA
0.2 plastic deformation, 1000 hr., ksi	NA	NA	NA

Ti-6Al-6V-2Sn Alloy Data
(Continued)

Properties	Temperature, F	
	RT	900
Stress-Rupture (transverse)		
Rupture, 100 hr., ksi	NA	NA
Rupture, 1000 hr., ksi	NA	NA
Stress Corrosion (c)		
80 TYS, 1000 hr. maximum	n	no cracks
Coefficient of Thermal Expansion		
5.3x10 ⁻⁶ in./in./F (68 F to 900 F)		
Density		
0.164 lb./in. ³		

(a) Values are average of triplicate tests conducted at "bottle" under the subject contract unless otherwise indicated. Various creep and stress-rupture values are from curves prepared using the results of a greater number of tests.

(b) Round-shoulder pin-type specimens; average of 3 tests in each direction.

(c) E, unattainable; NA, not attainable.

(d) Average of 4 tests in each direction.

(e) Results of tests at AFML in compact tension specimens.

(f) K_{ISCC} represents the algebraic ratio of initial stress to minimum stress in one cycle; that is, $K_{ISCC} = S_{min}/S_{max}$. K_{ISCC} represents the Wohler-Peterson theoretical stress concentration factor.

(g) Low-temperature three-point bend test. Alternate immersion in 3-17 NaCl.

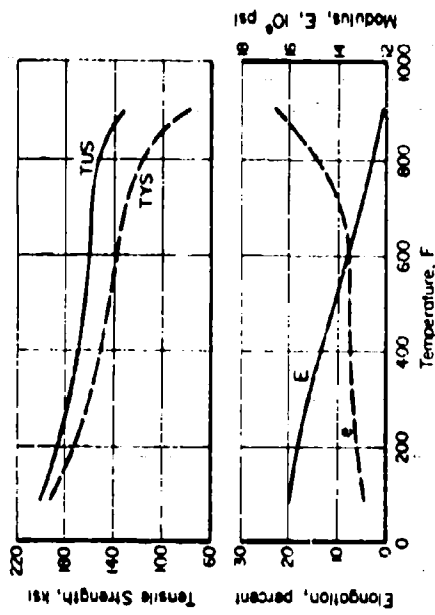


FIGURE 1. EFFECT OF TEMPERATURE ON THE TENSILE PROPERTIES OF SOLUTION TREATED AND Aged Ti-6Al-6V-2Sn (GENERAL) DIE FURNACES

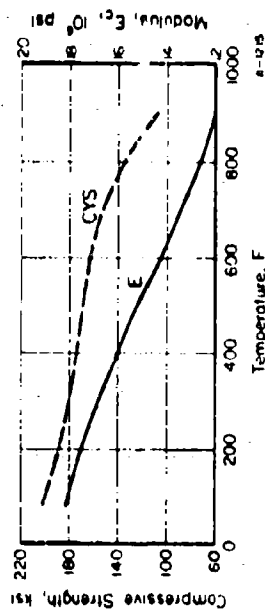


FIGURE 2. EFFECT OF TEMPERATURE ON THE COMPRESSIVE PROPERTIES OF SOLUTION TREATED AND Aged Ti-6Al-6V-2Sn (GENERAL) DIE FURNACES



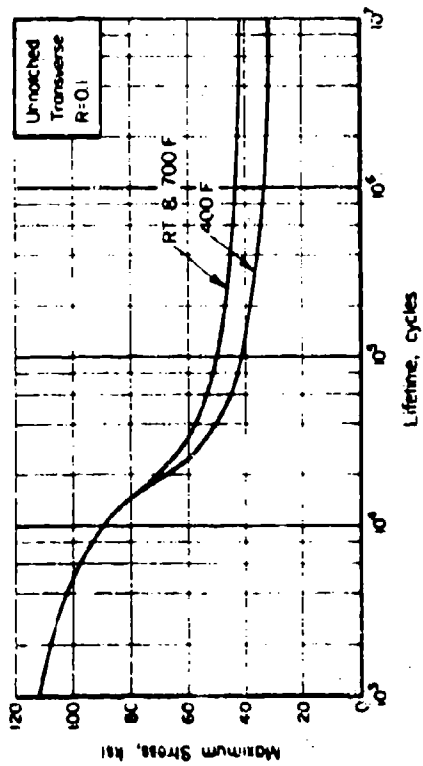


FIGURE 3. AVERAGE LIFETIME OF NOTCHED SIMILION TREATED MATERIALS UNDER ISOTHERMAL FATIGUE

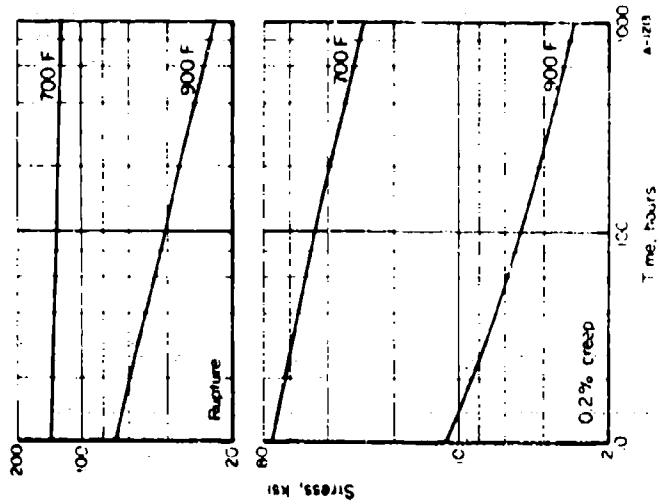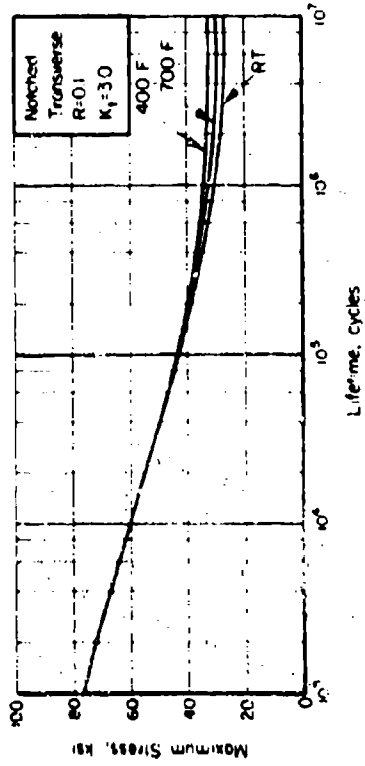

STRESS, ksi
TIME, hours
A-1218