

1983

MCIC-HB-01R
Volume 1



AD-A141 899

Damage Tolerant Design Handbook

A Compilation of Fracture and Crack-Growth Data
for High-Strength Alloys

DTIC FILE COPY

DTIC
SERIALIZED
JUN 07 1984
E

Metals and Ceramics Information Center
Battelle
Columbus Laboratories

Prepared by
University of Dayton Research Institute
Materials Laboratory
Air Force Wright Aeronautical Laboratories
Wright-Patterson Air Force Base

This document has been approved
for public release and sales; its
distribution is unlimited.

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER MCIC-HB-01R (4 Volumes)	2. GOVT ACCESSION NO. DA A141 899	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) DAMAGE TOLERANT DESIGN HANDBOOK. A COMPILATION OF FRACTURE AND CRACK-GROWTH DATA FOR HIGH-STRENGTH ALLOYS		5. TYPE OF REPORT & PERIOD COVERED
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) J. Gallagher		8. CONTRACT OR GRANT NUMBER(s) F33615-80-C-5149 DLA900-83-C-1744
9. PERFORMING ORGANIZATION NAME AND ADDRESS University of Dayton Research Institute 300 College Park Avenue Dayton, OH 45469		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
11. CONTROLLING OFFICE NAME AND ADDRESS Materials Laboratory (AFWAL/MLSE) Air Force Wright Aeronautical Laboratories (AFSC) Wright-Patterson AFB, OH 45433		12. REPORT DATE December 1983
		13. NUMBER OF PAGES 3260
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for Public Release; Distribution Unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Availability: Metals and Ceramics Information Center, P.O. Box 8128, Columbus, Ohio 43201 HC \$400.00 for 4 Volumes (No copies furnished by DTIC)		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) *Fracture (Mechanics), *Handbooks, *Titanium Alloys, *Nickel Alloys, *Stainless Steel, *Aluminum Alloys, High Strength Alloys, Structural Steel, Fracture Toughness, Damage Assessment, State of the Art, Data Compilation, Fatigue Crack Growth		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) This edition entirely revamps the 1975 edition. This edition is arranged by alloy rather than by property as in the previous addition. The data are presented in eight chapters and four volumes. Plane-strain fracture toughness (K_{Ic}), critical plane stress fracture toughness, apparent fracture toughness, R-curve, fatigue crack growth rates, sustained-load crack growth rate and threshold stress intensity (K_{ISCC}) data are presented for stainless steels, titanium alloys, nickel-base alloys, alloy steels, 2000-, 6000- and 7000-series aluminum alloys.		

**DAMAGE TOLERANT DESIGN HANDBOOK
MCIC-HB-01R**

ABOUT THIS HANDBOOK —

The **Damage Tolerant Design Handbook** was prepared by University of Dayton Research Institute under U.S. Air Force sponsorship and is being distributed by the Metals and Ceramics Information Center (MCIC). Its purpose is to provide a single comprehensive reference source on available fracture mechanics data for structural metal alloys of particular interest for aircraft and aerospace application.

SUPPLEMENTS —

It is intended that, as new data are generated on the fracture characteristics of structural alloys, supplements to this Handbook will be published by MCIC. Further updating and expansion of the current edition will result in supplements as significant data become available. Minor additions, errata, and inserts will be distributed as information becomes available.

KEEPING YOUR HANDBOOK UP TO DATE —

In order that we may keep all holders of the **Damage Tolerant Design Handbook** advised of supplements and new reference data, a registry of the location of all copies will be maintained. To assist us, we ask that you complete and return one of the self-addressed postcards (following this page) upon initial receipt of the Handbook. If responsibility for this copy is transferred to another party, please use one of the other postcards to advise us of the change. If there are no postcards, simply write to MCIC at the address below.

YOUR ASSISTANCE IS SOLICITED —

Although a substantial and continuing effort is made to include all available appropriate fracture mechanics data in this Handbook, we recognize that important sources may have been inadvertently overlooked and, of course, that new data are regularly being generated. Should you or your organization be able to provide additional pertinent data, MCIC — and other users of this reference Handbook — will be most appreciative. To be useful, data should include the supporting facts regarding material, condition, and test specimens and procedures. If you can assist us in this respect, please call or submit such data to MCIC at the address below. Many thanks

ADDITIONAL INFORMATION —

Specific questions about, or information for, the **Damage Tolerant Design Handbook** should be addressed to the attention of Mr. Harold Mindlin at:

Metals and Ceramics Information Center
BATTELLE
Columbus Laboratories
505 King Avenue
Columbus, Ohio 43201

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	<i>ET A HCO PL</i>
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-121	

Volume 1

Damage Tolerant Design Handbook

A Compilation of Fracture and Crack Growth
Data for High-Strength Alloys

Compiled by

J. Gallagher

Program Manager

University of Dayton Research Institute

Dayton, Ohio

Sponsored by

Materials Laboratory

Air Force Wright Aeronautical Laboratories
Wright-Patterson Air Force Base, Ohio 45433

December 1983

Metals and Ceramics Information Center

BATTELLE

Columbus Laboratories

505 King Avenue

Columbus, Ohio 43201

ACKNOWLEDGMENT

This document was published by the Metals and Ceramics Information Center (MCIC), Battelle's Columbus Laboratories, 505 King Avenue, Columbus, Ohio 43201-2693. MCIC's objective is to provide a comprehensive current resource of technical information on the development and utilization of advanced metal- or ceramic-base metals.

MCIC is publishing this revised and expanded edition of the Damage Tolerant Design Handbook to increase the availability of information to the technical community. The loose leaf format was selected to facilitate updating the handbook as new information becomes available. This edition is a completely revised and expanded version of the original handbook first published by MCIC in 1972 and revised in 1973 and 1975.

The Center is operated by Battelle-Columbus under Contract Number DLA900-83-C-1744 for the U.S. Defense Logistics Agency; technical aspects of MCIC operations are monitored by the Office of the Deputy Under Secretary of Defense Research and Advanced Technology. The support of these sponsor organizations is gratefully acknowledged.

This document was prepared under the sponsorship of the Department of Defense. Neither the United States Government nor any person acting on behalf of the United States Government assumes any liability resulting from the use or publication of the information contained in this document or warrants that such use or publication will be free from privately owned rights.

Approved for public release; distribution unlimited.

All rights reserved. This document, or parts thereof, may not be reproduced in any form without written permission of the Metals and Ceramics Information Center.

FOREWORD

This report has been prepared as AFWAL-TR-83-4144 to summarize the results of a damage-tolerant-material-property collection and reporting program conducted under USAF Contract No. F33615-80-C-5149, Damage Tolerant Design Handbook. The Materials Laboratory of Air Force Wright Aeronautical Laboratories (AFWAL/ML) was the sponsor; Mr. G. J. Petrak (AFWAL/MLSE) of the System Support Division was the Project Monitor. The University of Dayton was the contractor; the University of Dayton Research Institute (UDRI) conducted the work under the general supervision of Dr. J. P. Gallagher, program manager, and Mrs. Patricia L. Stumpff, principal investigator. Miss Elizabeth L. Johnson was responsible for the development of the software system that both stored the damage tolerant data and created the handbook graphical and tabular reports. Dr. P. W. Hovey developed the analytical french curve method used to describe the mean trend subcritical crack growth behavior. Other UDRI employees who provided extensive support for the creation of the handbook are: Dr. A. P. Berens, Mrs. Joanda D'Antuono, Mrs. JoAnn D. Jones, Miss Ellen M. Bornhorst, Miss Mary E. Stander, and Mr. Kevin Sullivan.

The Handbook could not have been produced without the extensive support given to the data collection effort by the following organizations and individuals:

ORGANIZATION

Aeronautical Systems Division
(Wright-Patterson AFB)

AiResearch

Alcoa

Armco

Army Material and Mechanics Research Center

Battelle-Columbus

Boeing-Commercial

Boeing Military

Fairchild-Republic

Federal Aviation Administration

Flight Dynamics Laboratory
(Wright-Patterson AFB)

General Dynamics—Ft. Worth

General Dynamics—Convair

CONTRIBUTORS

E. Davidson, J. F. Gonzalez, T. King,
and J. Lincoln

R. Graves, A. Hammond, D. W. McGrath, D. Ng,
D. Schwab, and H. Walters

R. J. Bucci, R. C. Malcolm, E. H. Spuhler, and
R. H. Wygonik

P. O. Metz

R. Chait

S. Ford, R. C. Rice, and H. Mindlin

U. Goranson and C. K. Gunther

F. K. Fox, J. J. Horsley, C. F. Tiffany,
and L. Wright

J. Arrighi, H. W. Kleindienst, and M. Levy

T. Swift

A. Gunderson and J. Rudd

V. Juarez, S. Manning, and J. W. Morrow

T. Spamer, C. Tanner, E. Spier, and W. E. Witzell

ORGANIZATION

General Electric
 Goodyear Aerospace
 Grumman Aerospace
 Howmet Co.
 Hughes Helicopter
 Kaiser Aluminum and Chemical Corp.

 Lawrence Livermore Nat. Lab.
 Lockheed-California
 Lockheed-Georgia

 Lockheed—Palo Alto
 Martin Marietta Aluminum
 Materials Laboratory
 (Wright-Patterson AFB)
 Materials Research Laboratory
 McDonnell-Douglas (St. Louis)
 McDonnell-Douglas (Long Beach)
 McDonnell-Douglas Astro.

 Naval Research Laboratory
 NASA-Langley Research Center

 NASA-Lewis
 Northrop Corp.

 Ogden Air Logistics Center (Hill AFB)

 Oklahoma City Air Logistics Center
 (Tinker AFB)
 Reynolds Metals Co.
 Rockwell International—Aircraft Division
 Rockwell International—Shuttle Orbiter Division
 Rockwell International—Rocketdyne Division
 San Antonio Air Logistics Center (Kelly AFB)
 Sandia Laboratories
 Sikorsky Aircraft
 TRW (Defense and Space Systems)

CONTRIBUTORS

L. Beitch, A. Coles, P. Domas, and R. Spuhler
 D. A. Venkatu
 H. L. Eidinoff
 D. E. Macha
 A. G. Hirko
 L. J. Barker, K. R. Brown, K. R. Hasse, and
 N. L. Pearson
 R. Streit
 T. R. Brussat, and D. Pettit
 E. J. Batch, C. S. Chu, A. C. Fehrle,
 and T. M. Hsu
 M. J. Rebholz
 D. Mellem
 C. Harmsworth, J. Larsen, and T. Nicholas

 E. J. Ripling and J. T. Santner
 H. Dill, C. R. Saff, and D. Rich
 P. Abelkis, H. C. Schjelderup, and D. S. Warren
 J. M. Davidson, R. M. Fujita, T. R. Murray, and
 A. P. Penton, III
 T. W. Crooker and J. A. Hauser
 C. M. Hudson, W. S. Johnson and
 J. C. Newman
 T. Orange
 J. Carter, V. C. Frost, A. F. Liu, P. Porter,
 P. Tanouye, and D. P. Wilhelm
 A. P. Allen, H. A. Johnson, D. King,
 J. Pearson-Smith, and A. Watson
 R. Meadows
 F. E. Loftin, G. R. Shockley, and R. E. Zinkham
 T. Kutko, J. Stolpestad, and J. Young
 C. D. Brownfield and R. M. Ehret
 S. Bashir and R. P. Jewett
 D. Schneider, J. Turner, and T. J. White
 J. Munford
 G. E. Lattin, and M. J. Rich
 J. C. Lewis

ORGANIZATION

University of Dayton Research Institute
Warner Robins Air Logistics Center
(Robins AFB)
Watervliet Arsenal
Westinghouse Hanford

CONTRIBUTORS

R. R. Cervay
J. Lewis and J. Wagner
J. Underwood
L. A. James

THE LOST ACKNOWLEDGMENT

It never fails in projects like these, that in the course of making absolutely sure that we acknowledge each and every individual who helped make it possible, **WE LEAVE SOMEONE OUT!** In the event that this happened, please accept our apologies and our gratitude for whatever it was that you did.

Damage Tolerant Design Handbook

Volume 1

CONTENTS

CHAPTER 1 HANDBOOK ORGANIZATION AND CONTENT

Overview
 Organization
 General Comments About Sorting Order and Abbreviations
 Material Chapter Summaries
 Alloy Section Summaries
 Alloy Fracture Toughness Subsection Formats
 Alloy Subcritical Crack Growth Subsection Formats

CHAPTER 2 METHODS OF CALCULATIONS

Overview
 Plane-Strain Fracture Toughness (K_{Ic})
 Critical Plane Stress Fracture Toughness
 The Apparent Fracture Toughness
 R-Curve (K_R Versus Δa_{eff})
 Fatigue Crack Growth Rate
 Sustained-Load Crack Growth Rates
 Threshold Stress Intensity (K_{Ithc})

CHAPTER 3 STAINLESS-STEEL ALLOYS

AFC 260	Custom 455	15-5 PH (VM)
AFC 77	PH 13-8Mo	17-4 PH
AFC 77(VAR)	PH 14-8 Mo	17-7 PH
AM 355	PH 15-7 Mo	304
AM 362	15-5 PH	316
AM 364	15-5 PH (AM)	347

CHAPTER 4 TITANIUM ALLOYS

BETA	Ti-5Al-2.5Sn	Ti-6Al-6V-2.5Sn
BETA C	Ti-6-2-2-2-2	Ti-6Al-2Sn-4Zr-6Mo
BETA III	Ti-6-2-4-2	Ti-8Al-1Mo-1V
Corona 5	Ti-6-2-4-6	Ti-8Mo-8V-2Fe-3Al
Ti-6Al-2Sn-2Zr	Ti-6Al-4V	Ti-5Al-2.5Sn (ELI)
-2Mo-2Cr-.25Si	Ti-6Al-4V(ELI)	Ti-6Al-6V-2Sn (ELI)
Ti-4Al-3Mo-IV	Ti-6Al-6V-2Sn	

Damage Tolerant Design Handbook

Volume 2

CONTENTS

CHAPTER 5 NICKEL BASE ALLOYS

Astroloy P/M-H
Astroloy P/M-W
Astroloy 901
Incoloy 901

Inconel 600
Inconel 625
Inconel 718
IN 100

IN 100 P/M-G
NASA IIB-7 P/M
P/M Rene 95
Waspaloy

CHAPTER 6 ALLOY STEELS

AF 1410
AF 1410 (VIM-VAR)
A 286
D6 AC
HP 9-4-.20
HP 9-4-.20 (CEVM)
HP 9-4-.25
HP 9-4-.30
HP 9-4-.45
HY-TUF
HY-150
HY-180

H11
10Ni Steel
12-9-2 (MAR)
12Ni-5Cr-3Mo
18Ni (180) MAR
18Ni (200) MAR
18Ni (250) MAR
18Ni (280) MAR
18Ni (300) MAR
300M
300M (AM)
300M (VAR)

300M (VM)
4140
4330V (MOD)
4340
4340 (AM)
4340 (DH)
4340 (EFM)
4340 V
4340 (VAR)
4340 (MOD)

Damage Tolerant Design Handbook

Volume 3

CONTENTS

CHAPTER 7 2000 AND 6000 SERIES ALUMINUM ALLOYS

2014	2024 (Alclad)	2324
2020	2048	2419
2020 (Alclad)	2124	2618
2021	2214	6061
2024	2219	

CHAPTER 8 7000 SERIES ALUMINUM ALLOYS

7001	7039
7005	7049
7007	7050
7010	7050 (Alclad)

Damage Tolerant Design Handbook

Volume 4

CONTENTS

CHAPTER 8 7000 SERIES ALUMINUM ALLOYS

7075	7090	7178
7075 (Alclad)	7091	7178 (Alclad)
7079	7149	7475
7079 (Alclad)	7175	7475 (Alclad)
7080		

CHAPTER 1
HANDBOOK ORGANIZATION AND CONTENT

1.0	OVERVIEW	1-1
1.1	ORGANIZATION	1-2
1.2	GENERAL COMMENTS ABOUT SORTING ORDER AND ABBREVIATIONS	1-5
1.3	MATERIAL CHAPTER SUMMARIES	1-7
1.4	ALLOY SECTION SUMMARIES	1-18
1.5	ALLOY FRACTURE TOUGHNESS SUBSECTION FORMATS	1-21
1.6	ALLOY SUBCRITICAL CRACK GROWTH SUBSECTION FORMATS	1-28

CHAPTER 1
HANDBOOK ORGANIZATION AND CONTENT

TABLE OF CONTENTS

<u>SECTION</u>		<u>PAGE</u>
1.0	OVERVIEW	1-1
1.1	ORGANIZATION	1-2
1.2	GENERAL COMMENTS ABOUT SORTING ORDER AND ABBREVIATIONS	1-5
	1.2.1 <u>Sorting Order</u>	1-5
	1.2.2 <u>Abbreviations</u>	1-5
1.3	MATERIAL CHAPTER SUMMARIES	1-7
	1.3.1 <u>Available Data Summary</u>	1-7
	1.3.2 <u>Plane Strain Fracture Toughness Material Data Summary</u>	1-12
	1.3.3 <u>Plane Stress and Transitional Fracture Material Data Summary</u>	1-12
	1.3.4 <u>Fatigue Crack Growth Rate Material Data Summary</u>	1-16
	1.3.5 <u>Stress Corrosion Cracking Threshold Material Data Summary</u>	1-18
1.4	ALLOY SECTION SUMMARIES	1-18
1.5	ALLOY FRACTURE TOUGHNESS SUBSECTION FORMATS	1-21
	1.5.1 <u>Plane Strain Fracture Toughness</u>	1-21
	1.5.2 <u>Plane Stress Fracture Toughness Data</u>	1-25
	1.5.3 <u>R-Curve Data</u>	1-28
1.6	ALLOY SUBCRITICAL CRACK GROWTH SUBSECTION FORMATS	1-28
	1.6.1 <u>Fatigue Crack Growth Rate Data</u>	1-28
	1.6.2 <u>Sustained Load Crack Growth Rate</u>	1-37
	1.6.3 <u>Stress Corrosion Cracking Threshold</u>	1-41

CHAPTER 1
LIST OF ILLUSTRATIONS

<u>FIGURE</u>		<u>PAGE</u>
1-1	ASTM Abbreviations Used to Describe Specimen Orientations.	1-10
1-2	Sample Data Summary Table, Taken from Table 3.0.1 (Stainless Steel Alloys).	1-11
1-3	Summary of Plane Strain Fracture Toughness (K_{IC}) Data, Taken from Table 3.0.2 (Stainless Steel Alloys).	1-13
1-4a	Format for Plane Stress and Transitional Fracture Toughness Data where Specimens were Constrained from Buckling. Example from Table 4.0.3, Titanium Alloys.	1-14
1-4b	Format for Plane Stress and Transitional Fracture Toughness Data where Specimens were not Constrained from Buckling. Example taken from Table 6.0.3, Alloy Steels.	1-15
1-5	Summary of Fatigue Crack Growth Rate Data, taken from Table 3.0.3 (Stainless Steel Alloys).	1-17
1-6	Summary of Stress Corrosion Cracking Threshold Material Data, taken from Table 3.0.4 (Stainless Steel Alloys).	1-19
1-7	Alloy Summary Format for Plane-Strain Fracture Toughness Data, Taken from Table 3.8.1.1, PH13-8Mo Stainless Steel.	1-20
1-8	Format for Alloy Fatigue Crack Growth Rate Data Summary, Data Taken from Table 3.8.1.4, PH13-8Mo Stainless Steel.	1-22
1-9	Format for Plane Strain Fracture Toughness Data. Example taken from AFC 77 Stainless Steel Alloys, Table 3.2.2.1.	1-24

CHAPTER 1
LIST OF ILLUSTRATIONS
(Concluded)

<u>FIGURE</u>		<u>PAGE</u>
1-10	Format for Plane Stress Fracture Toughness Data; Example taken from Table 3.9.2.1, PH14-8Mo Stainless Steel Alloy.	1-27
1-11	Format for Resistance Curve (R-Curve) Data. Example taken from Figure 7.5.2.6, 2024 Aluminum Alloy.	1-29
1-12	Graphical Format of the Fatigue Crack Growth Rate Data; Example Taken from Figure 3.8.3.14 Based on Stainless Steel Alloy PH13-8Mo Showing Effect of Stress Ratio.	1-30
1-13	Tabular Format for Fatigue Crack Growth Rate Data; Tabular Data Corresponds to Graphical Data Shown in Figure 1.12. Example taken from Table 3.8.3.14, PH13-8Mo Stainless Steel Alloy.	1-36
1-14	Graphical Format for Sustained Load Crack Growth Rate Data. Example taken from Figure 3.2.2.1, AFC77 Alloy Stainless Steel.	1-38
1-15	Tabular Format of Sustained Load Crack Growth Rate Data. Example taken from Table 3.2.3.1, AF77 Stainless Steel Alloy.	1-39
1-16	Format for Stress Corrosion Cracking Threshold Data; Example taken from Table 3.2.3.2, AF77 Stainless Steel Alloy.	1-42

CHAPTER 1
LIST OF TABLES

<u>TABLE</u>		<u>PAGE</u>
1.1	ORDER OF CHAPTERS	1-3
1.2	ORGANIZATION OF THE XTH MATERIAL CHAPTER	1-4
1.3	SORTING ORDER OF VARIOUS FIELDS	1-6
1.4	ABBREVIATIONS FOR MATERIAL SYSTEMS	1-8
1.5	ABBREVIATIONS FOR ALLOY CONDITIONING AND HEAT TREATMENTS	1-8
1.6	ABBREVIATIONS FOR PRODUCT FORMS	1-8
1.7	ABBREVIATIONS FOR ENVIRONMENTAL SYSTEMS	1-9
1.8	ABBREVIATIONS FOR SPECIMEN DESIGNS	1-9
1.9	ORDERING SCHEME FOR ENVIRONMENT	1-23
1.10	REFERENCE NUMBER FOR NEW DATA AND THE ORGANIZATIONS OR JOURNALS ASSOCIATED WITH THESE DATA	1-26
1.11	LIST OF POSSIBLE SYMBOLS USED FOR EACH SPECIMEN IN THE GRAPHICAL PRESENTATION OF THE FATIGUE CRACK GROWTH RATE DATA	1-33
1.12	ALTERNATE PRODUCT FORM SORTING ORDER FOR CRACK PROPAGATION DATA	1-33

CHAPTER 1

HANDBOOK ORGANIZATION AND CONTENT

1.0 OVERVIEW

This edition of the Damage Tolerant Design Data Handbook has been entirely revamped since the last update in 1975. The major organizational change is that data are now presented and sorted by material (aluminum, titanium, etc.) and by alloy (2024, 6Al-4V, etc.) rather than by property (i.e., K_{Ic} , K_{Isc} , da/dN). The reorganization makes it possible to present all the pertinent damage tolerant data on a particular alloy within one chapter subsection. This new organization was suggested by aerospace engineers as being the format best suited for their use. Additionally, this format now conforms to other aerospace structural metals handbooks such as the Military Handbook-5 and Aerospace Structural Metals Handbook.

A survey was conducted at the beginning of this handbook program; over one-hundred aerospace design, materials, and structural engineers were canvassed for their comments relative to the proposed organization, formats, types of summaries and new data types. Many of the comments and suggestions received were incorporated into the final design of the handbook. The data types of greatest interest were found to be fracture toughness data, fatigue crack growth rate data and R-curves. Interest in specific materials were mainly for the nickel base and aluminum alloy materials.

Throughout the handbook, the data are presented in English units, i.e., $\text{ksi} \sqrt{\text{in.}}$ was the unit for the fracture toughness and applied stress intensity factor levels, and inches/hr or inches/cycle were the unit values for the growth rates. Metric units have been incorporated along with the English units on the graphical presentation of the sustained load and fatigue crack growth rate data, but limited space forced the decision not to include metric units for the tabular data.

1.1 ORGANIZATION

The handbook is divided into eight chapters and consists of four volumes. Following the first chapter on handbook usage and the the second chapter on methods of calculations are the six material chapters. The order of the chapters are as designated in Table 1.1. This order was selected to keep the data for a particular chapter together as much as possible while keeping the size reasonable and the four volumes approximately equal.

Table 1.2 depicts the basic organization of each material chapter. Within each material chapter, the data are further divided into a section of material summaries, followed by sections that contain the data for individual alloys. The first number of any section, subsection, table or figure number refers to the chapter or material as designated in Table 1.1. The second number will run consecutively from zero on. A zero in the second position indicates that the data is a material summary; each succeeding second number indicates a new alloy, with the highest second number referring to the bibliography for that material chapter.

In a given material summary section, i.e., X.0, there are five possible material summary tables listed as subsections. Tables will be listed in the order defined by Table 1.2. If not enough data are available for a particular summary, this summary will not be printed and the next summary will pick up the sequence number. Section 1.3 describes the formats for the material summaries.

In each alloy section, e.g., Sections X.1, X.2, etc., the third number in the sequence will designate whether the data are (1) an alloy summary, (2) fracture toughness data, or (3) crack growth resistance data. Within each subsection, the data tables and graphs are ordered consecutively.

TABLE 1.1
ORDER OF CHAPTERS

<u>VOLUME NUMBER</u>	<u>CHAPTER</u>	<u>TITLE</u>
1	1	Handbook Organization, Content, and Formats
1	2	Methods of Calculations
1	3	Stainless Steel Alloys
1	4	Titanium Alloys
2	5	Nickel Base Alloys
2	6	Alloy Steel Alloys
3	7	2000 and 6000 Series Aluminum Alloys
3 and 4	8	7000 Series Aluminum Alloys

TABLE 1.2
ORGANIZATION OF THE XTH MATERIAL CHAPTER

SECTION X.0 - Material Summaries

- X.0.1 - Available Data Material Summary
- X.0.2 - Plane Strain Fracture Toughness Material
Data Summary
- X.0.3 - Plane Stress and Transitional Fracture
Toughness Data Summary
- X.0.4 - Fatigue Crack Growth Rate Comparison
Material Data Summary
- X.0.5 - Stress Corrosion Cracking Threshold Material
Data Summary

SECTION X.1 - First Material Alloy

- X.1.1 - Alloy Summaries
 - X.1.1.1 - Plane Strain Fracture Toughness Summary
 - X.1.1.2 - Fatigue Crack Growth Rate Data Summary
- X.1.2 - Fracture Toughness Data
 - X.1.2.1 - Plane Strain Fracture Toughness Data for
Alloy Number One
 - X.1.2.2 - Plane Stress and Transitional Fracture
Toughness Data for Stainless Steel
Alloy Number One
 - X.1.2.3 - R-Curves
- X.1.3 - Subcritical Crack Growth Data
 - X.1.3.1 - Fatigue Crack Growth Rate Data Data
(Tables and Plots) for Alloy Number One
 - X.1.3.2 - Sustained Load Crack Growth Rate Data
 - X.1.3.3 - Stress Corrosion Cracking Threshold Data
for Alloy Number One

SECTION X.2 - Second Material Alloy

SECTION X.N - Last Material Alloy

SECTION X.N+1 - Bibliography for the Chapter

There are three possible types of fracture toughness data: plane-strain fracture toughness data, plane stress and transitional fracture toughness data, and resistance curve data; Section 1.5 provides a detailed discussion of the data formats. There are three possible types of subcritical crack growth data: fatigue crack growth rate data, sustained load crack growth rate data, and stress corrosion cracking threshold data; Section 1.6 details the formats used to present these data.

To aid the handbook user locate data, examples of actual tables and figures follow. These examples are presented to familiarize the user with the formats presented in the handbook. Each table or figure is discussed as it is presented. The discussion follows the same order as that found in the handbook.

1.2 GENERAL COMMENTS ABOUT SORTING ORDER AND ABBREVIATIONS

1.2.1 Sorting Order

Table 1.3 describes the sorting order for all mechanical property data types. The left column lists the primary (material) data fields that have been sorted; the right column then lists the specific sorting order of each material data field. In all the following discussions, when a primary data field is noted as being sorted, the order of the sorting is as listed in Table 1.3. The primary data fields are also sorted; however, because the different data fields have different significance for individual mechanical property types, the sorting order is noted as each mechanical property data format is discussed. For all property data types, the property data are generally sorted in the order of first five primary data fields listed in Table 1.3.

1.2.2 Abbreviations

To ensure that all the necessary information is presented in the data tables and figures, specific abbreviations have been employed throughout the handbook. The abbreviations can be broken down into six categories that cover the following

TABLE 1.3
SORTING ORDER OF VARIOUS FIELDS

<u>DATA FIELD</u>	<u>SORTING ORDER</u>
1. Alloy	Blank Punctuation Marks (e.g., -) Alphabetic Characters (e.g., T) Numeric Characters (e.g., 6)
2. Condition/Heat Treatment	Blank Punctuation Marks Alphabetic Characters Numeric Characters
3. Product Forms	Sheet Plate Forging Extrusion Forged Bar Billet Casting Round Bar Welded and Stress Relieved Weldment Disk Extruded Bar Rolled Bar Bar
4. Test Temperatures	Negative Test Temp. (-423°F, -300°F) From 0°F to 65°F (0°F, 32°F etc.) From 65°F to 80°F (R.T.) Above 80°F (85°F, 200°F, etc.)
5. Specimen Orientation	L-S L-T T-S T-L S-T S-L L-C C-L L-R R-L R-C C-R
6. Yield Strength	Lowest to Highest
7. Buckling Constraints	Buckling of Crack Edges Not Restrained Buckling of Crack Edges Restrained Buckling of Crack Edges Unknown

data fields: (1) material, (2) condition/heat treatment, (3) product form, (4) environment, (5) specimen design, and (6) specimen/crack orientation. The abbreviations and associated descriptions for these six categories can be found in Tables 1.4 through 1.8 and Figure 1.1, respectively.

1.3 MATERIAL CHAPTER SUMMARIES

Material summaries are presented at the beginning of each chapter before any alloy summaries or detailed data. These summaries are meant to aid in the selection of materials for design and for basic comparisons of property data. There are five possible material summaries (see Table 1.2), each of which compare availability or properties of damage tolerant data for the given alloys, heat treatments, and product forms of a particular material. The five summaries immediately follow the text of introductory remarks that discuss the data for that material.

1.3.1 Available Data Summary

Figure 1.2 is the first page of the available data summary for the stainless steel chapter. As noted, the first number in the data summary table is a "3" which indicates that this is the third chapter; the second number is a "0" indicating that this is a material summary; the third number is a "1" which indicates that this is the first table in the material summary section. Note that the table numbers for subsequent data summaries only change in the third digit, except for the fatigue crack growth rate summary (see below).

The available data summary defines the property data that are available in the chapter by alloy, by condition/heat treatment, and by product form. The six different types of data are listed generally across the top of the table; an "x" is marked in the appropriate column to identify the particular property data that exists for the given alloy, condition/heat treatment, etc. The alloys are listed in the order that they appear in the handbook using the sorting order outlined in Table 1.3. This sorting order was created using a system

TABLE 1.4
ABBREVIATIONS FOR MATERIAL SYSTEMS

<u>Abbreviation</u>	<u>Materials</u>
ALUM	Aluminum Alloys
TITAN.	Titanium Alloys
NICKEL	Nickel-Base Alloys
STAIN. STEEL	Stainless Steel Alloys
ALLOY STEEL	Steel Alloys

TABLE 1.5
ABBREVIATIONS FOR ALLOY CONDITIONING AND HEAT TREATMENTS

<u>Abbreviation</u>	<u>Condition/Heat Treatment</u>
OQ	Oil Quenched
ABQ	Aus-Bay Quench
AC	Air Cool
WC	Water Quench
MA	Mill Anneal
BA	Beta Anneal
DA	Duplex Anneal
RA	Recrystallize Anneal
ST	Solution Treated
STA	Solution Treated And Aged

TABLE 1.6
ABBREVIATIONS FOR PRODUCT FORMS

<u>Abbreviations</u>	<u>Product Form</u>
S	Sheet
P	Plate
E	Extrusion
F	Forging
FB	Forged Bar
BT	Billet
BR	Round Bar
RB	Rolled Bar
C	Casting
W	Weldment
D	Disk
EB	Extruded Bar
B	Bar


TABLE 1.7
ABBREVIATIONS FOR ENVIRONMENTAL SYSTEMS

<u>Abbreviations</u>	<u>Environmental System</u>
R. T.	Room Temperature (65°F-80°F)
L. H. A.	Low Humidity Air (< 10% RH)
Dry Air	Low Humidity Air (< 10% RH)
H. H. A.	High Humidity Air (> 80% RH)
Lab. Air	Laboratory Air (% RH unspecified)
Dist. H ₂ O	Distilled Water
Dist. Water	Distilled Water
3.5 PCT Nacl	3.5% Salt Water Solution
JP.4	JP-4 Aircraft Fuel
JP.4 - Fuel	JP-4 Aircraft Fuel
S. T. W.	Sump Tank Water
S. S. W.	Simulated Sea Water
S. C. S.	Shop Cleaning Solvent
F. C. S.	Field Cleaning Solvent
Salt Fog	Salt Fog
Temp.	Temperature


TABLE 1.8
ABBREVIATIONS FOR SPECIMEN DESIGNS

<u>Abbreviations</u>	<u>Specimen Design*</u>
CT	Compact Tension
NB	3Pt. Notched Bend
WOL	Wedge Open Load
CCP	Center Cracked Panel
BWOL	Bolt Loaded-Wedge Open Load
CANT	Cantilever Beam
TDCB	Tapered Double Cantilever Beam
CHAR	Charpy
PTSC	Part Through Surface Crack
SENT	Single Edge Notch Tension
K _B BAR	K _B Bar
4-NB	4 Pt. Notched Bend
MCT	Modified Compact Tension
CNT	Center Notched Tension
DCB	Double Cantilever Beam
BDCB	Bolt Loaded Double Cantilever Beam


*Also note that when "SG" is used in conjunction with a specimen design, the specimen is side-grooved along the path of the crack.

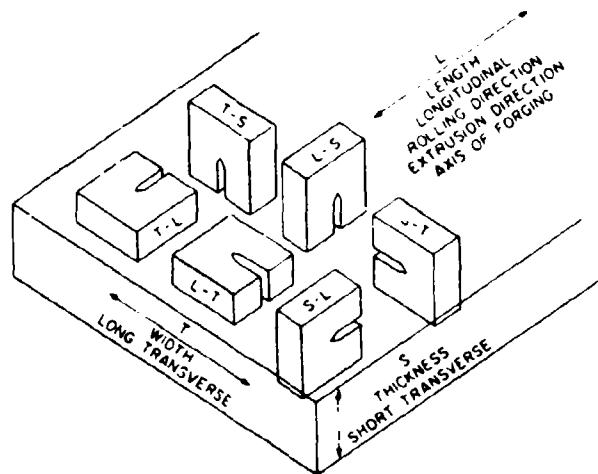

(a) Crack Plane Orientation Code for Rectangular Sections

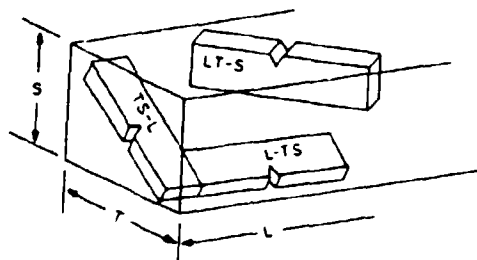

(b) Crack Plane Orientation Code for Rectangular Sections Where Specimens are Tilted with Respect to the Reference Directions

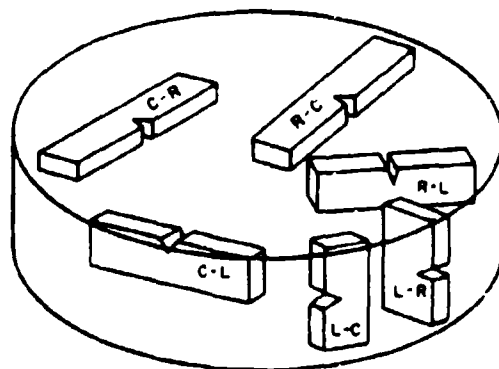

(c) Crack Plane Orientation Code for Bar and Hollow Cylinder

Figure 1.1. ASTM Abbreviations Used to Describe Specimen Orientations.

Table 3.0.1
 AVAILABLE DATA FOR STAINLESS STEEL ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	MTC	KC	R CURVES	DA/DN	DA/DT	MISCC
AFC 260	2200F 1HR 1900F 1HR DG -100F 1HR -320F 1HR 800F 2+2 HR	PLATE						X
	2200F 1HR 1900F 1HR DG -100F 1HR -320F 1HR 1050F 2+2HR	PLATE						X
	2200F 1HR 1900F 1HR DG -100F 1HR -320F 1HR 900F 2+2 HR	PLATE						X
	2200F 1HR 1900F 1HR DG -100F 1HR -320F 1HR 1000F 2+2 HR	PLATE						X
AFC 77	AUSTENIZED AT 2010F. QUENCHED & TEMPERED AT 810F	SHEET					X	
	1800F 1HR DG, -100F 0.5HR, 500F 2+2 HR (COARSE GRAIN)	PLATE						X
	1800F 1HR DG, -100F 0.5HR, 1000F 2+2 HR (COARSE GRAIN)	PLATE	X					X
	1800F 1HR DG, -100F 0.5HR, 500F 2+2 HR (FINE GRAIN)	PLATE						X
	1800F 1HR DG, -100F 0.5HR, 1000F 2+2 HR (FINE GRAIN)	PLATE	X					X
	1800F 1HR, DG, -100F 0.5HR, 700F 2+2HR (COARSE GRAIN)	PLATE	X					X
	1800F 1HR, DG, -100F 0.5HR, 800F 2+2HR (COARSE GRAIN)	PLATE	X					X
	1800F 1HR, DG, -100F 0.5HR, 700F 2+2HR (FINE GRAIN)	PLATE	X					X
	1800F 1HR, DG, -100F 0.5HR, 800F 2+2HR (FINE GRAIN)	PLATE	X					X

Figure 1.2. Sample Data Summary Table, Taken From Table 3.0.1
 (Stainless Steel Alloys).

sort of the database and sorts the alloys with designations using blanks, punctuation marks and alphabetic characters first with numeric characters following. Heat treatments and conditions are also sorted in this same manner. Following the sort by alloy and by condition/heat treatment, the property data are then sorted according to product form. The particulars of the sorting by product form are also outlined in Table 1.3 with sheet data listed before plate, forging, extrusion, etc.

1.3.2 Plane Strain Fracture Toughness Material Data Summary

The first page of the stainless steel, plane-strain fracture-toughness-data summary is shown in Figure 1.3. This is the second possible material summary and the third table digit is "2". The data are again sorted and separated on the data fields of alloy, condition/heat treatment and product form. All data listed are for room temperature (65°F - 80°F) laboratory air only. Plane strain fracture toughness mean values and standard deviations are listed for the three major orientations; that is, L-T, T-L and S-L. Product thickness range and minimum specimen thicknesses are listed for general information. Dashes in a particular column indicate that no mean plane strain fracture toughness data exist for the stated conditions.

1.3.3 Plane Stress and Transitional Fracture Material Data Summary

The plane stress and transitional fracture toughness data summary is presented third in the series of summaries. Figure 1.4 illustrates that these tables are presented as a function of whether the data are collected using specimens with or without buckling constraints. Note that in Figure 1.4 (all available titanium data) and 1.4b (all available alloy steel data) that the data are sorted by alloy, condition/heat treatment, test temperature, specimen orientation and specimen width. Yield strength is not a sorting field but is given for general information. The mean K_{IC} values are listed as a function of specimen thickness which is indicated across the top of the page.

TABLE 3.0.2
PLANE STRAIN FRACTURE TOUGHNESS VALUES OF STAINLESS STEEL ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/II	PRODUCT FORM	NAME OF PRODUCT THICKNESS (IN)	K _{IC} (KSI SQRT(IN))							
				L-T		S-L					
				SPECIMEN THICK * MEAN	STD DEV	SPECIMEN THICK * MEAN	STD DEV				
AFC 77 (VAR)	1700F 1HR. 00 2100F 1HR. MOVED TO FCE AT 1923F. WELD 1HR. 00. -100F 2*HR. 900F. 2*2HR	FORGING	6 00	0 50	48 6	3 1	0 50	30 8	1 3		
				2 01	110 5	4 9	2 01	108 0	5 7		
CUSTOM 435	1500F 1HR. 00. 950F 4HR. AC	FORGING	4 00	0 48	72 1	7 8					
				0 48	46 2	3 3					
PH13-6PH	ANNEALED AUSTENITE COND FORCED BAN AND TRANSFORMED AT 38F. AGED 1015F	FORGING	3 00	1 01	114 1	13 7	1 00	99 6	22 4		
				1 63	103 0	19 4	1 63	89 6	1 8		
H 950	SHEET	FORGING	1 00-2 25	1 00	58 4	6 5	1 00	69 4	16 1		
				1 00	70 3	16 0					
		ROLLED BAN	2 35	1 00	64 9	2 9	1 00	63 5	1 7	7 1	
				1 00	105 6	4 8	1 00	96 2	5 2		
		H1000	SHEET	4 00	2 75-8 00	0 98	94 7	3 6			
						0 75	101 6	11 0	0 75	88 1	17 1
	EXTRUSION	1 50	1 00	68 5	5 5	1 00	66 2	2 1			

* MINIMUM SPECIMEN THICKNESS (IN)

Figure 1.3. Summary of Plane Strain Fracture Toughness (K_{IC}) Data, Taken from Table 3.0.2 (Stainless Steel Alloys).

TABLE 4.0.3

PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS OF
TITANIUM ALLOYS (WITH BUCKLING CONSTRAINTS)

Alloy	Condition/Ht	Test Temp. (°F)	Specimen Orient	Specimen Width (in.)	Yield Strength (KSI)	Specimen Thickness (in.)	K_{IC} (KSI \sqrt{in})
Ti-5Al-2.5Sn	Annealed	-423	L-T	3.0	203	116.8/4.5 (5)	0.040
				6.0	203	109.4/6.6 (9)	
				12.0	203	104.2/4.0 (8)	
				16.0	203	97.1/9.6 (2)	
			T-L	12.0	210	147.6/28.9 (2)	
Ti-6Al-4V	HA	R. T. -110	L-T	24.0	136	196.4/19.9 (6)	
			T-L	8.0	163	159.4/7.5 (3)	
Ti-6Al-4V (ELI)	Annealed	R. T.	L-T	18.0	136	161.6/6.5 (5)	
Ti-8Al-1Mo-1V	D. A.	R. T.	L-T	12.0	136	111.7/15.0(3)	
				20.0	134	220.5/15.8(4)	

^aMean/Standard Deviation (No. of Specimens)

Figure 1.4a. Format for Plane Stress and Transitional Fracture Toughness Data where Specimens were Constrained from Buckling. Example from Table 4.0.3, Titanium Alloys.

TABLE 6.0.3
 PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS OF
 STEEL ALLOYS (WITHOUT BUCKLING CONSTRAINTS)

Alloy	Condition/Ht	Test Temp. (°F)	Specimen Orient	Specimen Width (in)	Yield Strength (Ksi)	Specimen Thickness (in) - 0.025	K_c^a (Ksi $\sqrt{\text{in}}$)
18 Ni(300) MAR	----	-423	L-T	4.0	386	86.4/7.3 (5)	
		-320	L-T	2.0	336	142.6/7.4 (5)	
	L-T		4.0	336	124.7/8.0 (5)		
		R. T.	L-T	2.0	277	132.1/4.3 (5)	
			L-T	4.0	277	128.5/3.8 (5)	
				L-T	18.0	277	110.3/10.9 (3)

^a Mean/Standard Deviation (No. of Specimens)

Figure 1.4b. Format for Plane Stress and Transitional Fracture Toughness Data Where Specimens Were Not Constrained from Buckling. Example from Table 6.0.3, Alloy Steels.

Individual K_c data values are listed only if useful in determining a trend in the data. Specimen thickness variations run along the top of the page and may vary from one table to another in order to prevent overcrowding the tables while still accommodating all of the data.

1.3.4 Fatigue Crack Growth Rate Material Data Summary

An example fatigue crack growth rate (FCGR) summary is presented in Figure 1.5 where the data are taken from the Stainless Steel Chapter. Note that the data are from Table 3.0.3.1, a four number sequenced designation. The first two numbers again indicate the chapter (3) and the summary section (0). The third number in the sequence (3) indicates that this is the third ordered table in the material summary (Note that insufficient plane stress and transitional fracture toughness data were available for this material so no summary table of the K_c type was generated). The fourth number in the sequence (1) indicates that this is the first ordered table in the fatigue crack growth rate summary. Readers will find one table for each specimen orientation for which there is enough data for the table to have meaning.

All data in a particular table were collected under conditions where the stress ratio (R) is between 0.0 and 0.1, and the environment is room temperature and laboratory air; the loading frequencies vary slightly depending on the individual tests. The range of test conditions are listed at the top of each table. Beneath the general description of test conditions are the data fields of alloy, condition/heat treatment and product form for which the FCGR data comparisons can be made. The ΔK (Delta K) levels are listed across the top of the table and are identical to some of the levels associated with the tabular format of the mean trend FCGR data, i.e., at levels of 2.5, 5.0, 10.0, 20.0, 50.0, 100.0 Ksi $\sqrt{\text{in.}}$ (see Section 1.6 for a listing of all mean trend ΔK levels). The fatigue crack growth rates in units of 10^{-6} inches/cycles, are listed in the appropriate columns and rows according to the alloy, condition/heat treatment, and product form for which they apply. With this format, it is easy to determine which materials, heat

Table 3.0.3.1

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR STAINLESS STEEL ALLOYS

TEST CONDITIONS.

SPECIMEN ORIENTATION: Unknown ENVIRONMENT: LAB AIR AT R. T.
 STRESS RATIO 0.05-0.10 FREQUENCY: 3.00-30.00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)		
					FOR DELTA K LEVELS (MSI SORT(IN)) =	20.0	50.0
304	ANNEALED	SHEET	0.05	10.00	.163	3.07	
	ANNEALED	SHEET	0.05	15.00	.130	2.83	
	ANNEALED	SHEET	0.10	1.67		2.84	
	ANNEALED	SHEET	0.10	6.00		2.56	
	ANNEALED & AGE	PLATE	0.05	3.00		1.38	
316	ANNEALED AT 1950F, 1HR, NO	PLATE	0.05	10.00		2.39	
347	050 IN FROM CENTERLINE	WELDMENT	0.10	30.00		9.83	
	AT CENTERLINE	WELDMENT	0.10	30.00		13.1	
	AT HEAT AFFECTED ZONE	WELDMENT	0.10	30.00		17.9	

Figure 1.5. Summary of Fatigue Crack Growth Rate Data, Taken from Table 3.0.3 (Stainless Steel Alloys).

treatments, or product forms have the lowest growth rate at a particular ΔK level. For example, based on the data given in Figure 1.5, annealed and aged 304 stainless steel performs better than annealed 304 stainless steel.

1.3.5 Stress Corrosion Cracking Threshold Material Data Summary

Figure 1.6 illustrates, using Table 3.0.4, the format for the stress corrosion cracking threshold material data summary, the fifth possible material data summary. Because of the small number of specimens (typically one or two) that are used to generate these data, individual results are presented here rather than means and standard deviations. The data are sorted by alloy, condition/heat treatment, product form and specimen orientation. Possible environments for which K_{ISCC} data exist are listed across the top of the table; K_{ISCC} data values for each particular environment are listed in the appropriate row and column. This table summary allows for comparisons of K_{ISCC} values of various materials in a particular environment as well as a quick assessment of how various environments affect a particular material.

1.4 ALLOY SECTION SUMMARIES

Following the material summaries, the data were divided into sections by alloy. Each alloy section is further subdivided into three subsections: a summary subsection, a fracture toughness subsection, and a crack growth resistance subsection. The data content and format for these three subsections are described in this and the following two subsections, respectively.

There are two possible alloy summaries, a plane strain fracture toughness summary and fatigue crack growth rate data summary. Figure 1.7 presents the tabular format for the K_{IC} alloy summary. It is similar to the K_{IC} material summary in that the mean and standard deviation for a particular condition/heat treatment, product form and specimen orientation is given for each alloy. However, the number of specimens used to generate the data has been added. The data has also been sorted by product form first, then condition/heat treatment and specimen orientation.

TABLE 3.0.4

INDIVIDUAL STRESS CORROSION CRACKING THRESHOLD DATA FOR STAINLESS STEEL ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ FIT	PRODUCT FORM	SPECIMEN ORIENTATION	S _{ISCC} (ksi/in)		
				SEAWATER	INDUST. ATMOSPHERE	
AFC 77	1800F 1HR O ₂ , -100F 0.5 HR, 500F 2&2 HR, (Coarse G.S.)	P	---	---	3.5% NaCl	20% NaCl
					15	50
	2000F 1HR O ₂ , -100F 0.5 HR, 700F 2&2 HR	B	---	---	3.5% NaCl	20% NaCl
					40	15
	2000F 1HR O ₂ , -100F 0.5 HR, 800F 2&2 HR	B	---	---	3.5% NaCl	20% NaCl
					10	30
	2000F 1HR O ₂ , -100F 0.5 HR, 900F 2&2 HR	B	---	---	3.5% NaCl	20% NaCl
					30	90
	2000F 1HR O ₂ , -100F 0.5 HR, 1100F 2&2 HR	B	---	---	3.5% NaCl	20% NaCl
					48	40
	2000F 1HR O ₂ , -100F 0.5 HR, 500F 2&2 HR, & 10PCT CW, 1000F	P	---	---	3.5% NaCl	20% NaCl
					40	45
	2000F 1HR O ₂ , -100F 0.5 HR, 500F 2&2 HR, & 20 PCT CW, 700F	P	---	---	3.5% NaCl	20% NaCl
					40	37
2200F 1HR, 1900F 1HR O ₂ , -100F 1HR, -300F 1HR, 900F, 2&2 HR	P	T-L	---	3.5% NaCl	20% NaCl	
				45	37	
2200F 1HR, 1900F 1HR O ₂ , -100F 1HR, -100F 1HR 1000F 2&2 HR	P	T-L	---	3.5% NaCl	20% NaCl	
				45	37	
2200F 1HR, 1900F 1HR O ₂ , -100F 1HR, -100F 1HR, 1050F 2&2 HR	P	T-L	---	3.5% NaCl	20% NaCl	
				45	37	
AFC 355	SCT 850	P	T-L	---	3.5% NaCl	20% NaCl
					8	24
AFC 1000	SCT 1000	B	T-L	---	3.5% NaCl	20% NaCl
					6	18
AFC 1000	SCT 1000	P	T-L	---	3.5% NaCl	20% NaCl
					37	52
AFC 1000	SCT 1000	B	T-L	---	3.5% NaCl	20% NaCl
					26	35
AFC 1000	SCT 1000	P	T-L	---	3.5% NaCl	20% NaCl
					8	24
AFC 1000	SCT 1000	B	T-L	---	3.5% NaCl	20% NaCl
					6	18
AFC 1000	SCT 1000	P	T-L	---	3.5% NaCl	20% NaCl
					37	52
AFC 1000	SCT 1000	B	T-L	---	3.5% NaCl	20% NaCl
					26	35

Figure 1.6. Summary of Stress Corrosion Cracking Threshold Material Data, Taken from Table 3.0.4 (Stainless Steel Alloys).

Table 3.8.1.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
STAINLESS STEEL ALLOY PH13-8MO AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION		(NUMBER OF SPECIMENS)	
	K_{IC}	S _D	I-L	S-L
<u>FORGED BAR</u>				
AUSTENITE COND AND TRANSFORMED AT 38F. AGED 1015F	103.0 ± 19.4 (2)	89.6 ± 1.8 (2)	---	---
M1000	114.2 ± 0.9 (2)	122.7 ± 3.0 (3)	---	---
<u>ROLLED BAR</u>				
M 950	66.9 ± 2.9 (3)	63.5 ± 1.7 (6)	74.1 ± 2.1 (3)	---
M1000	90.0 ± 7.1 (2)	75.0 ± 4.2 (2)	---	---
M1050	103.1 ± 4.6 (3)	94.8 ± 7.8 (6)	92.2 ± 4.2 (2)	---

Figure 1.7. Alloy Summary Format for Plane-Strain Fracture Toughness
Data, Taken from Table 3.8.1.1.1, PH 13-8Mo Stainless Steel.

This summary basically puts all the K_{IC} data for a particular condition and product form together for easy comparison. It also allows for a quick assessment of the effect that orientation has on the fracture toughness.

The FCGR alloy data summaries shown in Figure 1.8 are similar to the FCGR material data summaries described previously. Note that for a particular alloy, the data are separated by the test variables of specimen orientation and environment which are listed at the top of each page. Other test variables such as condition/heat treatment, product form, stress ratio and frequency are then listed for the data as noted. Typically, a number of FCGR data summaries are produced to describe the effects of specimen orientation and environments. Sorting on specimen orientation is as shown in Table 1.3 and sorting on environment is in the order described in Table 1.9. With these summary tables, it is possible to determine which condition/heat treatment and product form give the lowest FCGR in a given environment for a given specimen orientation. Discrepancies in data sets can also be noted as well as a quick determination of how stress ratio and frequency affect the data in a particular environment.

1.5 ALLOY FRACTURE TOUGHNESS SUBSECTION FORMATS

Within each alloy section following the alloy summaries is the fracture toughness type data. Fracture toughness data consists of plane strain data (K_{IC}), plane stress and transitional fracture toughness data (K_C), and resistance curve data (R-curves). Each of these has a different and yet somewhat similar ordering scheme which is particularly suited to that type of data.

1.5.1 Plane Strain Fracture Toughness

The format for the plane-strain fracture toughness data is shown in Figure 1.9. This particular example is taken from the stainless steel chapter for alloy AFC 77. The data are sorted by condition/heat treatment, then product form, test temperature, orientation and yield strength using the sorting order identified in Table 1.3. All K_{IC} data collected for these

Table 3.8.1.4
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 STAINLESS STEEL PH13-8MI

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: L.H.A.
 AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2.5	5	10	20	30	100
H1000	EXTRUDED BAR	0.08	6.00				2.22	20.8		
	EXTRUDED BAR	0.30	6.00				2.98			
H1000	FORGED BAR	0.08	6.00				5.82			
H1000	FORGED BAR	0.30	6.00				4.70			
H1000	FORGED BAR	0.50	6.00			0.51	4.70			
H1000	BILLET	0.00	6.00			0.34	4.02			
H1000	EXTRUDED BAR	0.08	6.00			0.33	3.73	34.4		
H1000	EXTRUDED BAR	0.50	6.00			0.85	5.59			
H1000	ROLLED BAR	0.08	1.00			0.29	3.57			
H1000	ROLLED BAR	0.00	6.00			0.29	3.40			
H1000	ROLLED BAR	0.30	6.00			0.62	4.39			
H1000	ROLLED BAR	0.50	6.00			0.79	5.09			

Figure 1.8. Format for Alloy Fatigue Crack Growth Rate Data Summary, Data Taken from Table 3.8.1.4, PH 13-8 Mo Stainless Steel.

TABLE 1.9
ORDERING SCHEME FOR ENVIRONMENT

Dry Air
Low Humidity Air
Negative Temperatures/Air
0°F to Room Temperature
Room Temperature/Laboratory Air
Above Room Temperature/Air
Argon
High Humidity Air
JP-4 Fuel
Water Saturated JP-4 Fuel
Alternating JP-4 Fuel
Distilled Water
Nitrogen
Solvent Cleaning Solution
3.5% NaCl
Sump Tank Water
Simulated Sea Water
Salt Fog
Field Cleaning Solvent

Table 3.2.2.1
STAINLESS STEEL AFC 77

CONDITION	--PRODUCT--		TEST SPECIMEN	YIELD STRENGTH (KSI)	SPECIMEN			K(IIC)	CRACK LENGTH (IN)	K(IIC)/√B (IN)	K(IIC) MEAN DEV (KSI√IN)	K(IIC) STAM DEV	DATE	REFER
	FORM	THICK (IN)			TEMP (F)	ORIENT	WIDTH (IN)							
1800F 1#R. 0#1. P 0 5# R T L-T	1000F 0 3#R. 1000F 2-2#R	COARSE GRAIN		173 0	1 500	0 500	N#	----	0 05		25 00		1969 74720 (1)	
1800F 1#R. 0#1. P 0 5# R T L-T	1000F 0 3#R. 7000F 2-2#R	COARSE GRAIN		183 0	1 500	0 500	N#	----	0 11		38 00		1969 74720 (1)	
1800F 1#R. 0#1. P 0 5# R T L-T	1000F 0 3#R. 8000F 2-2#R	COARSE GRAIN		208 0	1 500	0 500	N#	----	0 05		28 00		1969 74720 (1)	
1800F 1#R. 0#1. P 0 5# R T L-T	1000F 0 3#R. 7000F 2-2#R	FINE GRAIN		203 0	1 500	0 500	N#	----	0 15		49 00		1969 74720 (1)	
1800F 1#R. 0#1. P 0 5# R T L-T	1000F 0 3#R. 8000F 2-2#R	FINE GRAIN		224 0	1 500	0 500	N#	----	0 05		31 00		1969 74720 (1)	
1800F 1#R. 0#1. P 0 5# R T L-T	1000F 0 3#R. 1000F 2-2#R	FINE GRAIN		232 0	1 500	0 500	N#	----	0 04		30 00		1969 74720 (1)	
1800F 1#R. 0#1. BR 3 00 R T L-R	7000F 2-2#R			185 0	1 500	0 480	N#	----	0 14		44 00		1968 84302 (1)	
1800F 1#R. 0#1. BR 3 00 R T L-R	7000F 2-2#R			213 0	1 500	0 480	N#	----	0 03		29 00		1968 84302 (1)	
1900F 1#R. 0#1. BR 3 00 R T L-R	8000F 2-2#R			222 0	1 500	0 480	N#	----	0 28		74 00		1968 84302 (1)	
2000F 1#R. 0#1. BR 3 00 R T L-R	9000F 2-2#R			207 0	1 500	0 480	N#	----	0 29		70 00		1969 76136 (1)	
2000F 1#R. 0#1. BR 3 00 R T L-R	9000F 2-2#R			214 0	1 500	0 480	N#	----	0 17		56 00		1969 76136 (1)	

NOTE: (1) CHEMISTICALS: PERCENT: 0.18C, 0.10MN, 0.015P, 0.021S, 0.13SI, 0.21NI, 14.0CR, 3.02MO, 13.4CO, 0.27V, 0.05W
1#R-#R DATA ARE AVERAGE VALUES

Figure 1.9. Format for Plane Strain Fracture Toughness Data. Example Taken from AFC 77 Stainless Steel Alloys, Table 3.2.2.1.

same parameters are put together with the mean and standard deviation listed in a column near the right of the page. Product thickness is listed after product form, but is not a sorting parameter. Specimen dimensions including thickness, width and crack length are also listed, but are not listed in any particular order. The $2.5 (K_{IC}/\sigma_{ys})^2$ criterion value is included for information purposes only. Two additional columns list the date of the reference and the reference number so that an idea of when the data were collected can be assessed, and where additional information might be obtained should it be desired. Reference numbers from the earlier handbook have been retained and new data have been assigned a new reference number with the first two digits signifying the organization or journal from which the data was obtained. Table 1.10 lists the general format for new reference numbers. The final column at the right hand side of the page refers to the notes at the bottom and are used to indicate out-of-range compositions, average data values, and other identifying important features.

1.5.2 Plane Stress Fracture Toughness Data

The format for presenting plane stress fracture toughness (K_C) data is presented in Figure 1.10. The sorting format for the plane stress fracture toughness (K_C) data within a particular alloy section is by condition, then buckling of crack edges restrained, unrestrained, or unknown, and then by product form, test temperature, specimen orientation, specimen thickness and specimen width. Additionally, initial and final crack lengths are given as a function of the total crack length ($2a$) for center-cracked panel/specimens. Also, the onset and maximum gross stress values are listed when available. The fracture toughness parameters K_C and K_{app} are calculated as described in Chapter 2 and the individual as well as the mean and standard deviation values are listed for both K_C and K_{app} . The final two columns present the date of the reference and the reference number.

TABLE 1.10

REFERENCE NUMBERS FOR NEW DATA AND THE ORGANIZATIONS
OR JOURNALS ASSOCIATED WITH THESE DATA

1. ALxxx - Alcoa Laboratories - Alcoa Center, PA.
2. AMxxx - Airesearch Manufacturing - Los Angeles, CA.
3. BLxxx - Battelle Columbus Laboratories, Columbus, OH
4. BWxxx - Boeing Military Airplane Co., Wichita, KA
5. DAXxx - Douglas Aircraft - Long Beach, CA
6. EFMxx - Journal of Engineering Fracture Mechanics
7. FRxxx - Fairchild Republic - Farmingdale, N.Y.
8. GDxxx - General Dynamics - Fort Worth, TX
9. GExxx - General Electric - Evendale, OH
10. HDxxx - Westinghouse Hanford Development Lab., Richland, Wash.
11. LGxxx - Lockheed Georgia - Marietta, GA.
12. MAXxx - McDonnell Aircraft Co. - St. Louis, MO
13. MDxxx - McDonnell Douglas Astronautics Corp, Huntington Beach, CA.
14. MRxxx - Materials Research Laboratory - Glenwood, IL
15. NCxxx - Northrop Corporation - Hawthorne, CA
16. NLxxx - NASA Langley Research Center - Hampton, VA.
17. NRxxx - Naval Research Laboratories - Washington, DC.
18. PWxxx - Pratt & Whitney Aircraft Group - Government Products
Division - West Palm Beach Florida
19. RAXxx - Reynolds Metals Co. - Richmond, VA
20. RIxxx - Rockwell International - North American Division &
Shuttle Orbiter Div. - Los Angeles, CA.
21. UCxxx - University of Cincinnati - Cincinnati, OH
22. UDxxx - University of Dayton Research Institute, Dayton, OH
23. UMxxx - University of Missouri - Rolle, Missouri
24. WAXxx - Wright Aeronautical Laboratories- WPAFB, OH

Table 3.9.2.1

STAINLESS STEEL PH14-8MO		K(C)		CRACK LENGTH GROSS STRESS										K(C)				
CONDITION	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	---SPECIMEN---		INIT		FINAL		ONSET		MAX		K(APP) STAN		K(C) STAN		
				WIDTH (IN)	THICK (IN)	(IN)	(IN)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)	MEAN	DEV	MEAN	DEV	
	W	B	2A(F)	2A(F)	S(D)	S(MAX)												
SRH1050	S	0.03	63 L-T	174.5	24.040	0.025	3.990	---	72.60	231.63	---	---	---	---	---	---	1964	57573
SRH1050	S	0.03	R.T. L-T	174.5	7.990	0.025	2.010	---	118.10	218.44*	---	---	---	---	---	---	1964	57573
SRH1050	S	0.03	R.T. L-T	174.5	24.020	0.025	3.000	---	95.90	210.21	---	---	---	---	---	---	1964	57573
		0.03		174.5	24.030	0.025	6.000	---	72.40	231.22	---	---	---	---	---	---	1964	57573
		0.03		174.5	24.040	0.025	6.000	---	71.90	229.61	223.7/11.7	---	---	---	---	---	1964	57573
SRH1050	S	0.05	R.T. L-T	196.6	24.010	0.050	6.000	---	92.10	294.19	---	---	---	---	---	---	1964	57573
SRH1050	S	0.09	R.T. L-T	197.4	24.100	0.093	6.000	---	115.70	369.42	---	---	---	---	---	---	1964	57573

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

Figure 1.10. Format for Plane Stress Fracture Toughness Data; Example Taken from Table 3.9.2.1, PH14-8MO Stainless Steel Alloy.

1.5.3 R-Curve Data

The format for resistance curve (R-Curve) data is shown in Figure 1.11. The information listed at the top of the page includes the material type, the alloy, the condition/heat treatment, the product form, and the thickness if known, the specimen type and orientation, the specimen dimensions, thickness and width, the K_{Ic} value, if known, and the reference number. Unless otherwise specified, the data were taken at room temperature in laboratory air environments. Only one specimen is illustrated per figure, and the figures are sorted by alloy, condition/heat treatment, test temperature and environment, orientation and specimen thickness and width.

The resistance curve data are plotted on linear scales; K_R , the applied stress intensity, as a function of Δa_{eff} , the change in effective crack length (see Chapter 2 for the details associated with the calculation). There are two possible scales for the data; (1) the vertical scale ranging from 0 to 120 Ksi $\sqrt{in.}$ and horizontal scale ranging between 0.0 to 1.1 inches, and (2) the vertical scale ranging from 0.0 to 240 Ksi $\sqrt{in.}$ and the horizontal scale ranging between 0.0 and 3.3 inches. These two scales were chosen to accommodate all the data.

1.6 ALLOY SUBCRITICAL CRACK GROWTH SUBSECTION FORMATS

The subcritical crack growth data follow the fracture toughness data within each alloy section. The subcritical crack growth data includes: fatigue crack growth rate data, sustained load crack growth rate data, and stress corrosion cracking threshold data.

1.6.1 Fatigue Crack Growth Rate Data

The fatigue crack growth rate data are presented in two complementary formats - a graphical format and a mean trend tabular format. Figure 1.12 represents the graphical format which was chosen to present fatigue crack growth rate data. Basic information common to all data on a particular page is listed at the top of the page in the header section. Below

CONDITION/HT: T351
 FORM: .19" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

SPECIMEN THK: .181"
 SPECIMEN WIDTH: 11.988"
 K_{IC} (KSI \sqrt{in}):
 REFERENCE: DA001

ALUM. ALLOY
2024

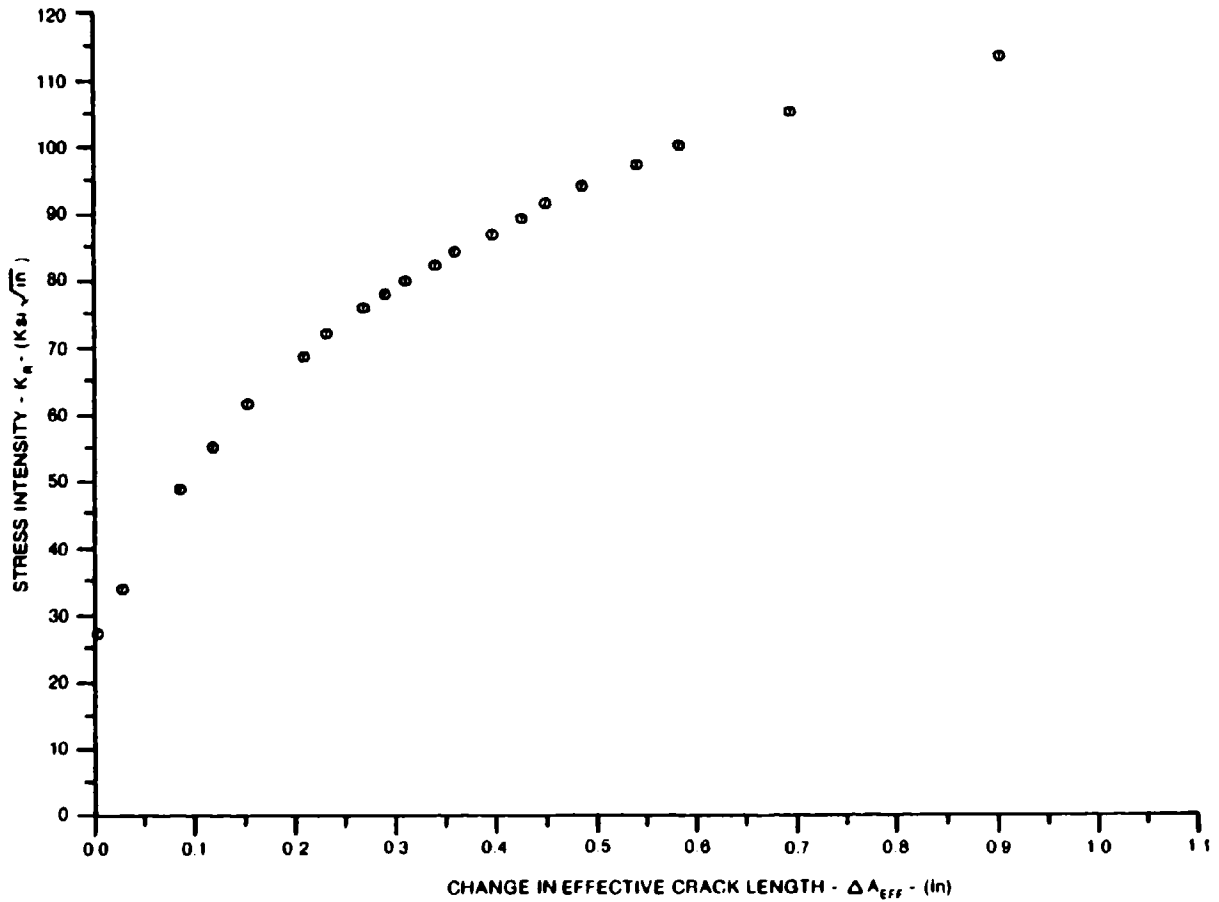


Figure 1.11. Format for Resistance Curve (R-Curve) Data.
 Example Taken from Figure 7.5.2.6, 2024
 Aluminum Alloy.

CONDITION/HT: H1300
 FORM: 1.00" TH FORGED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 1.0 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 218.0 KSI
 ULT. STRENGTH: 222.6 KSI
 SPECIMEN THK: 0.489- 0.504"
 SPECIMEN WIDTH: 3.982- 4.117"
 REFERENCES: G0009

STAIN.
 STEEL

PH13-8MO

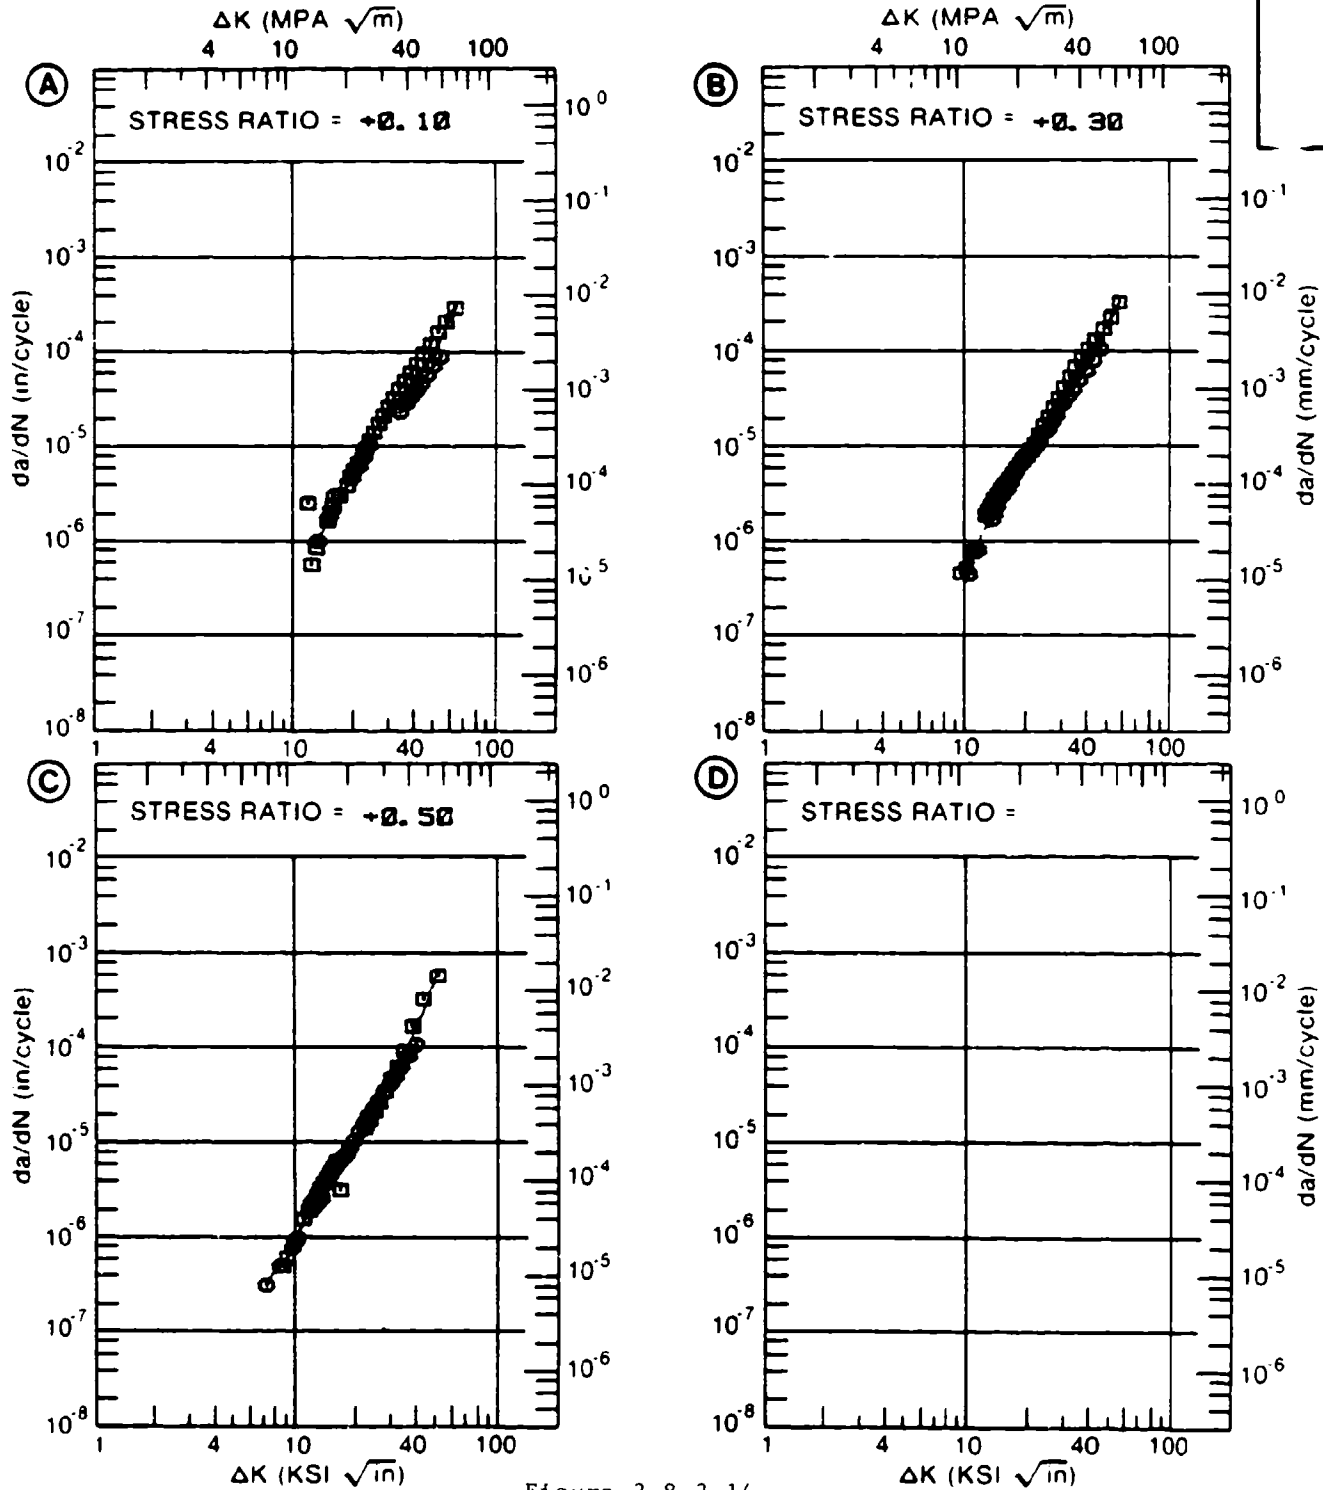


Figure 3.8.3.14

Figure 1.12. Graphical Format of the Fatigue Crack Growth Rate Data; Example Taken from Figure 3.8.3.14 Based on Stainless Steel Alloy PH13-8Mo Showing Effect of Stress Ratio.

the header section, there are four separate graphs on which the data are plotted. Each graph contains only data taken under identical conditions. Data are presented in each of the different graphs to show trends in behavior. The data on a page may describe the effects of one of three parameters: stress ratio, temperature/environment, and frequency. In order to accommodate these three variations, the header data at the top is slightly varied and the parameter being varied (e.g. stress ratio) is listed at the top of each of the active graphs as shown in Figure 1.12.

The header information at the top includes the material and alloy identifications listed in the small boxes in the upper right hand corner of each page for ease in locating the data. The condition/heat treatment is then listed at the top of the header. Below this, test and material parameters are listed in two columns; the first column listing the product form and product thickness, specimen type, specimen orientation and the two of the three parameters (i.e., stress ratio, test temperature/environment, frequency) not being varied on that particular page. The second column lists the room temperature tensile yield and ultimate strengths, the specimen dimensions of thickness and width, and the reference numbers identifying the data source.

All data are plotted as fatigue crack growth rate (da/dN) as a function of the range in the stress intensity factor (ΔK). The graphs are equal sized log-log plots ranging from 10^{-8} to 10^{-1} inches/cycle for the growth rates (i.e., seven decades), and from 1 to 200 Ksi $\sqrt{\text{in}}$ for values of ΔK . The definition of ΔK according to ASTM Standard E647 was chosen for data presentation throughout the handbook, i.e., ΔK = the maximum stress-intensity factor if the stress ratio is negative ($R \leq 0$). For other details, see Chapter 2.

English units, i.e., inches/cycle for growth rates and Ksi $\sqrt{\text{in.}}$ for ΔK , are listed to the left and the bottom of each page. Metric units, i.e., millimeters/cycle for growth rate values and megapascals $\sqrt{\text{m}}$ for ΔK , are listed at the top and right of each page.

By reviewing Figure 1.12, it can be noted that there are two different data symbols utilized in each graph. The two different symbols represent data from two different tests. Up to twenty different tests can be accommodated with the symbols defined in Table 1.11. Each graph, however, is restricted to a maximum of 300 da/dN- ΔK points; if the amount of data greatly exceeded these values, the data were separated onto two plots and the variable listed in each of the graphs is exactly the same. Mean trend curves have been established for each data set and can be seen going through the data on most of the graphs. The mean trend was developed using a cubic spline polynomial with the ability to control some aspects of the curve fit. The method is described in detail in Chapter 2. Fatigue crack growth rate data containing less than eight data points are plotted but mean trend curves were not established for these data.

Fatigue crack growth rate data are sorted slightly differently than fracture toughness data. Within a particular alloy, the data are sorted first by condition/heat treatment (using the order discussed in Table 1.3) then by product form and thickness with the order for product form defined as in Table 1.12. The product form order was altered to keep the data on forged and extruded bars near the data for forgings and extrusions, respectively. The sort on product thickness after product form is by increasing thickness. The next sort is by specimen orientation using the order defined by Table 1.3 and is followed by a sort by type of plot.

TABLE 1.11
LIST OF POSSIBLE SYMBOLS USED FOR EACH SPECIMEN
IN THE GRAPHICAL PRESENTATION OF THE FATIGUE
CRACK GROWTH RATE DATA

<u>Test Order No.</u>	<u>Symbol</u>	<u>Test Order No.</u>	<u>Symbol</u>
1	⊞	11	✕
2	⊙	12	✖
3	▲	13	✗
4	+	14	!
5	×	15	•
6	◆	16	◆
7	↑	17	■
8	✕	18	•
9	z	19	★
10	∨	20	—

TABLE 1.12
ALTERNATE PRODUCT FORM SORTING ORDER
FOR CRACK PROPAGATION DATA

Sheet
Plate
Bar
Billet
Disk
Extrusion
Extruded Bars
Forgings
Forged Bars
Rolled Bars
Round Bars
Castings
Weldments

In the final series of sorts, the data are ordered so that all the pages where the data varies on stress ratio are placed before the data that varies on test temperature/environment; these data are placed before any data which varies on frequency. When there are a number of stress ratio plots, within these data sets, the data are sorted by test temperature/environment using the order listed in Table 1.9. If there are a number of stress ratio plots which also have the same test temperature/environment, then the final sort is in order of decreasing frequency. Within the group of test temperature/environment plots that follow the stress ratio plots, these are also sorted additionally by increasing stress ratio then further by decreasing frequency if necessary. Within the group of frequency plots, which follow the temperature/environment plots, the data are further subdivided by increasing stress ratio and then by the test temperature/environment sort of Table 1.9 if necessary. The above organizational scheme was established for easy comparison of data and to define the effects that defined variables had on crack growth rate. For other types of comparisons, it may be necessary to search through a subsection to find all the data of interest.

As stated earlier, in addition to the graphical presentation there also exists a tabular format of the mean trend values. This format is presented in Figure 1.13. The tabular format and the graphical format will be presented side-by-side in the handbook with the tabular format on the left and the graphical format on the right. Figure 1.13 is the tabular format of the data presented in Figure 1.12. Note that the Table and Figure numbers are identical.

On examination of Figure 1.13, one can see that the Table can be broken up into six sections. These sections are identified as: (1) the header section, (2) the maximum ΔK - da/dN values section, (3) the mean trend fatigue crack growth rate values at the specified values of ΔK section, (4) the maximum ΔK - da/dN values section, (5) the root mean square percent error (RMSPE) section, and (6) the life prediction ratio section.

Section 1, the header section, does not include all the header information that is listed on the graphical format. Here only the material, alloy, condition/heat treatment and environment (if it is a stress ratio plot) are listed. Beneath the fatigue crack growth rate data header are the axes labels ΔK (Delta K) and da/dN . The letters A, B, C, and D, under the da/dN label, correspond to the same identifying letters on the four plots on the graphical format. Below these letters are the abbreviations of E for Environment, R for Stress Ratio, and F for Frequency which identifies the variable for this particular data set. Following these abbreviations are the values of the variables for this data.

Section 2 lists the minimum ΔK values to the left and the corresponding da/dN values in the appropriate column. These points present the slowest crack growth rate on the mean trend curves shown in Figure 1.12.

Section 3 lists the mean trend values. The ΔK values are listed to the left and the da/dN values are listed for each curve to the right in the appropriate column. However, the ΔK values are now fixed values and the growth rates in the columns correspond to these ΔK values for the individual graphs. There are 28 possible ΔK values ranging from 1 to 200 ksi $\sqrt{\text{in}}$; the specific values utilized are 1.0, 1.3, 1.6, 2.0, 2.5, 3.0, 4.0, 5.0, 6.0, 7.0, 8.0, 9.0, 10.0, 13.0, 16.0, 20.0, 25.0, 30.0, 40.0, 50.0, 60.0, 70.0, 80.0, 90.0, 100.0, 130.0, 160.0, and 200.0 Ksi $\sqrt{\text{in}}$.

Note that in Figure 1.13 all 28 ΔK values are not listed, only those in which there was a mean trend data available for at least one of the graphs. This means that in this case (Figure 1.12) all ΔK values less than 7.0 and greater than 60.0 Ksi $\sqrt{\text{in}}$ are not included since none of the curves had data outside this range.

Table 3.8.3.14

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.14 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000
ENVIRONMENT: R. T., H. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10***-6 IN./CYCLE)			
	A	B	C	D
	R=+0.10	R=+0.30	R=+0.50	
DELTA K MIN	A: 11.42 B: 9.13 C: 6.87 D:	.928	.466	.299
	7.00 8.00 9.00 10.00 13.00 16.00 20.00 25.00 30.00 35.00 40.00 50.00 60.00		.543	.342 .468 .625 1.08 3.06 5.84 11.6 24.3 47.9 91.9 174. 607.
DELTA K MAX	A: 62.14 B: 56.12 C: 50.46 D:	303.	339.	643.
ROOT MEAN SQUARE PERCENT ERROR	33.16	14.35	12.25	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	2	1	2

Figure 1.13. Tabular Format for Fatigue Crack Growth Rate Data; Tabular Data Corresponds to Graphical Data Shown in Figure 1.12. Example Taken from Table 3.8.3.14, PH 13-8Mo Stainless Steel Alloy.

Section 4 identifies the maximum (highest) $\Delta K - da/dN$ point on the mean trend curve in a manner similar to Section 2 which identified the lowest point on the curve.

Section 5, entitled "The Root Mean Square Percent Error" (RMSPE), is basically a description of scatter about the mean trend line; that is, a smaller value indicates a smaller scatter than a larger one. The calculation of this value is described in Chapter 2.

Section 6 presents life prediction information in terms of life prediction ratios. The life prediction ratio (LPR) is the number of cycles predicted (using the mean trend curve) divided by the actual number of cycles taken from the experimental crack length versus cycle data for a predefined interval. The actual LPR values are not listed but the results are summarized. The data summary is divided into five ranges, that is LPR's from: (1) 0.0-0.5, (2) 0.5-0.8, (3) 0.8-1.25, (4) 1.25-2.0, and (5) above 2.0. The numeric values in the columns across from the LPR range represents the number of specimens that had LPR's in that particular range. Because some data were received in reduced form only, i.e., (ΔK , da/dN) only, not all of the test specimens shown on the graphs will have LPR's, i.e., raw crack length versus cycle count data was not available for comparison. The LPR's generally were found to be in the center range, indicating an adequate mean trend fit of the data. For threshold type tests and for tests in which the loads were varied frequently through the test, LPR's tended to be outside this range.

1.6.2 Sustained Load Crack Growth Rate

The sustained load crack growth rate data are presented subsequent to the fatigue crack growth rate data and are plotted on log-log plots in a manner similar to the FCGR data (See Figure 1.14). Tabular mean trend formats are also presented where sufficient data exists (See Figure 1.15). The data are

CONDITION/HT: AUSTENITIZED AT 2010F, QUENCHED & TEMPERED AT 810F
 FORM: 0.00" TH SHEET
 SPECIMEN TYPE:
 ORIENTATION:
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK:
 SPECIMEN WIDTH:
 CRACK LENGTH (A₀):
 K_{ISCC}:
 REFERENCES: 95544

STAIN.
STEEL

AFC 77

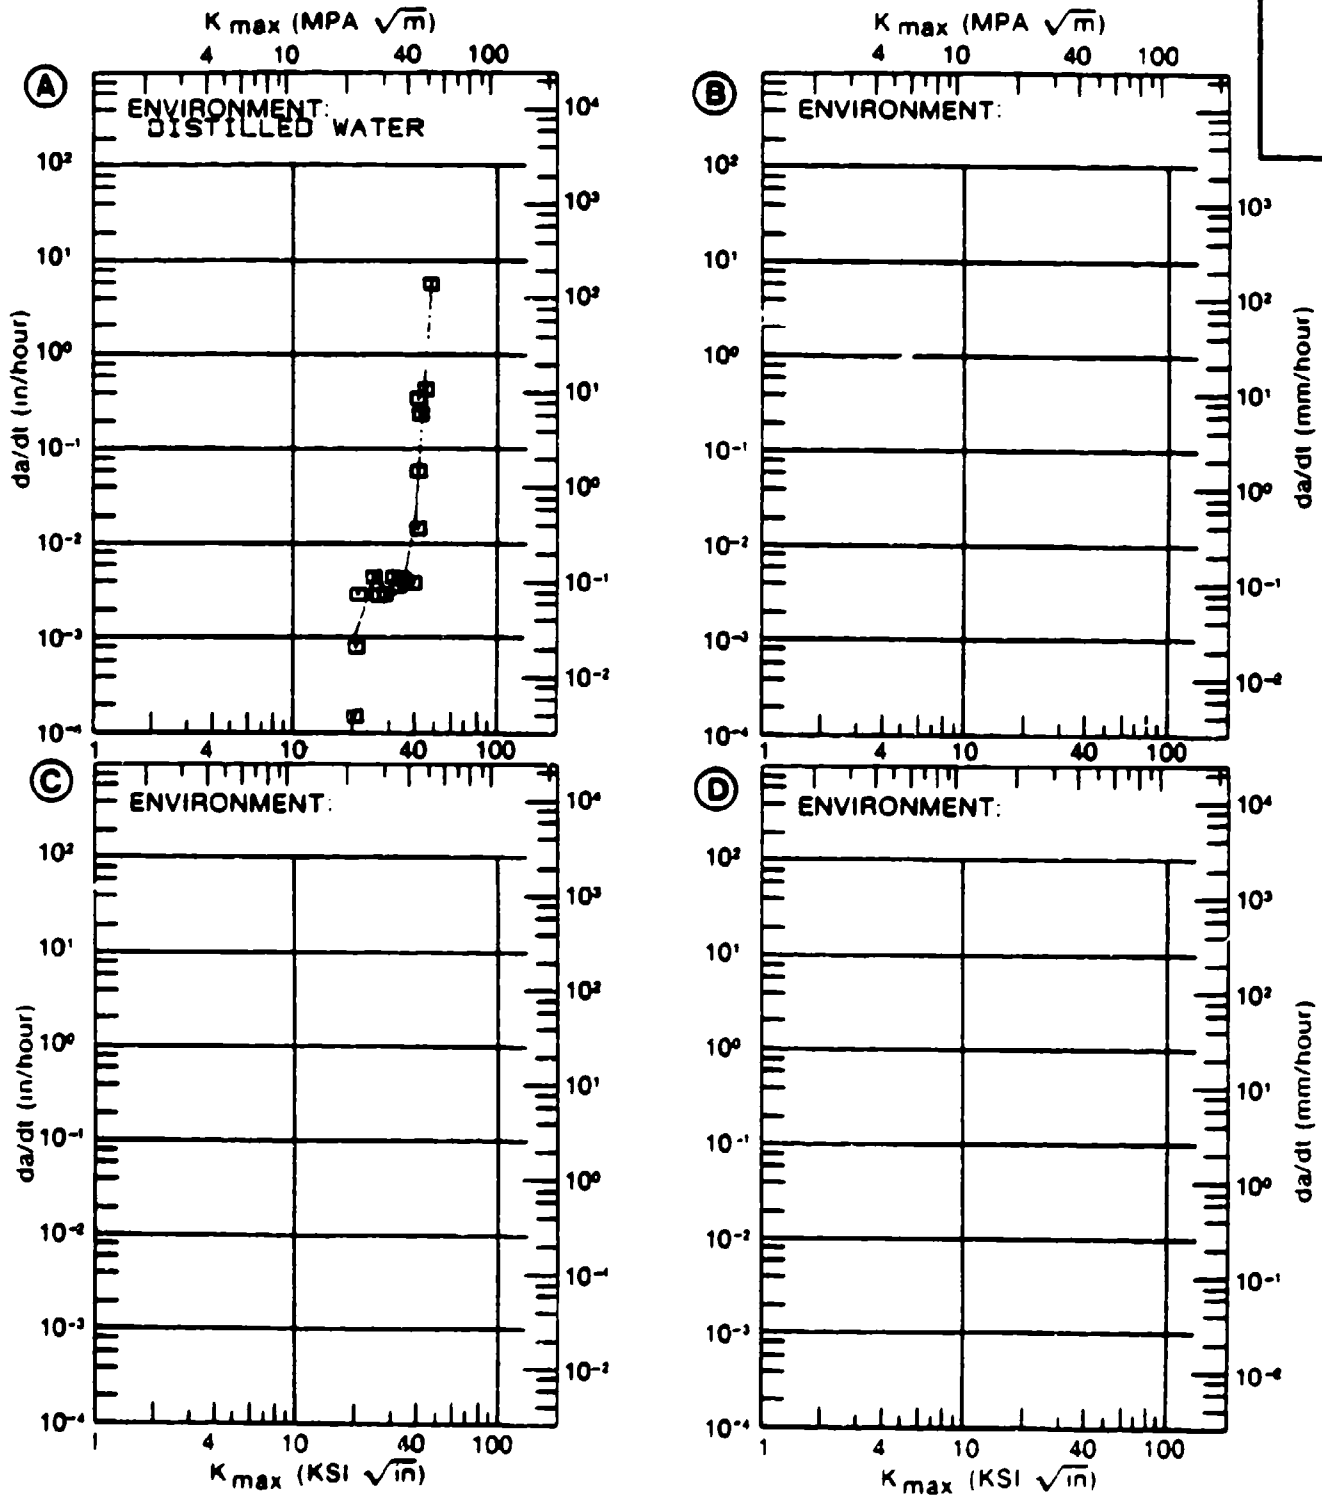


Figure 3.2.3.1

Figure 1.14. Graphical Format for Sustained Load Crack Growth Rate Data. Example Taken from Figure 3.2.3.1, AFC 77 Alloy Stainless Steel.

TABLE 3.2.3.1

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.2.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL AFC 77

CONDITION: AUSTENITIZED AT 2010F, QUENCHED & TEMPERED AT 810F

K MAX (KSI*IN**1/2)		DA/DT (10**-3 IN/HOUR)			
		A	B	C	D
		E = DISTILLED WATER			
K MAX MIN	A: 20.00	1.01			
	B:				
	C:				
	D:				
	25.00	4.55			
	30.00	2.67			
	35.00	3.21			
	40.00	17.5			
K MAX MAX	A: 47.00	5213.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		62.42			
PERCENT ERROR					

Figure 1.15. Tabular Format of Sustained Load Crack Growth Rate Data. Example Taken from Table 3.2.3.1, AFC 77 Stainless Steel Alloy.

plotted to present time based crack growth rate as a function of maximum stress-intensity factors on pages with header sections and four graphs of equal size with both English and Metric units lining the sides. Again, the header information includes the material and the alloy in the small boxes in the upper right hand corner of the pages. The condition/heat treatment is listed at the very top and the rest of the parameters are listed in two columns beneath the condition. The first column contains the parameters of form, form thickness, specimen type, specimen orientation, and test temperature/environment, while the second column contains the tensile yield strength, specimen thickness and width, initial crack length (a_0), stress corrosion cracking threshold values, K_{ISCC} , and the reference numbers. As before, there are also three variations on these plots, that is, variations on form and form thickness, tensile yield strength, and test temperature/environment. There are also some data sets in which condition/heat treatment for a given alloy is varied; these variations were manually designated on the plots. In addition to the three basic plot variations noted, the sustained load crack growth rate data have two possible growth rate axes. In order to accommodate the data, the two sets of axes chosen were 10^{-6} to 10^0 inches/hr. and 10^{-4} to 10^2 inches/hour (English units). Both have maximum stress-intensity values that range from 1 to 200 Ksi $\sqrt{\text{in.}}$

Some of these data also have mean trend curves and mean trend tables associated with them. The mean trend tables are again presented directly opposite to the graphical presentation of the data, similar to that done for the fatigue crack growth rate data. Figure 1.15 is the tabular format of the data in Figure 1.14. The format of this table is similar to the fatigue crack growth rate data, so little further explanation is warranted. All of these data were received in reduced form, and therefore, no LPR's are given; due to the nature of the data, the values of the RMSPE are usually larger than for the FCGR data. Additionally, mean trend curves representative of the data were not always created; for these cases, no mean trend curve or table is presented.

1.6.3 Stress Corrosion Cracking Threshold

Following the sustained load crack growth rate data is the tabular stress corrosion cracking threshold data. An example of this data format is presented in Figure 1.16, which is similar to the fracture toughness data format. The material, alloy and data type are listed at the top of the sheet. To the left, the condition/heat treatment is listed, then product form, product thickness, test temperature, specimen orientation, yield strength, and environment. Following these parameters are the specimen thickness, width and design as well as crack length, fracture toughness, K_{ISCC} individual values, mean values, standard deviations, test times, dates and reference numbers.

The data are sorted according to (material, alloy) condition/heat treatment, product form, test temperature, specimen orientation and environment. The order of the sorts are identified in Table 1.3 except for environment which is sorted by the utility sort, i.e., by a sort similar to that for alloy and condition/heat treatment.

The fracture toughness values presented, $K(Q)$, only indicate the level of crack toughness of the material; these values were obtained from the threshold tests and are not valid plane-strain fracture toughness values. The $K(Q)$ values, however, should provide an engineer with an indication of stress-corrosion cracking sensitivity relative to fracture.

In the K_{ISCC} tabular data, there are two columns in which asterisks (*) may appear; the column on specimen design and the column on K_{ISCC} . All asterisks that appear in the specimen design column indicate that the specimen has been side-grooved along the path of the crack; note (* = SG) at the top of the column. The asterisks that appear in the K_{ISCC} column behind the individual K_{ISCC} values indicate that the crack length and/or specimen thickness were not greater than $2.5 (K_{ISCC}/\sigma_{ys})^2$, as noted at the bottom of the page.

Table 3.2.3.2

STAINLESS STEEL AFC 77		K (ISCC)										
CONDITION	--PRODUCT-- FORM THICK OR (IN)	TEST SPEC TEMP OR (F)	YIELD STR (KSI)	ENVIRONMENT	SPECIMEN		CRACK LENGTH K(G) (IN)	K (ISCC) (KSI*SQRT IN)	MEAN DEV	STAN DEV	TEST TIME (MIN)	DATE REFER
					WIDTH (IN)	THICK (IN)						
					A	B						
1800F 1HR 0G, P -100F 0.5HR, 500F 2+2 HR (COARSE GRAINED STRUCTURE)	0.56	R.T.	154.0	3.5 PCT NAACL	1.500	0.480	CANT*	119.00	92.00*			1969 74720
1800F 1HR 0G, P -100F 0.5HR, 1000F 2+2 HR (COARSE GRAINED STRUCTURE)	0.56	R.T.	173.0	3.5 PCT NAACL	1.500	0.480	CANT*	25.00	15.00			1969 74720
1800F 1HR 0G, P -100F 0.5HR, 500F 2+2 HR (FINE GRAINED STRUCTURE)	0.56	R.T.	196.0	3.5 PCT NAACL	1.500	0.480	CANT*	111.00	97.00*			1969 74720
1800F 1HR 0G, P -100F 0.5HR, 1000F 2+2 HR (FINE GRAINED STRUCTURE)	0.56	R.T.	232.0	3.5 PCT NAACL	1.500	0.480	CANT*	30.00	20.00			1969 74720
2000F 1HR 0G, B -100F 0.5HR 1400F 2+2 HR	3.00	R.T.	150.0	3.5 PCT NAACL	1.500	0.480	CANT*	116.00	80.00*			1969 76136
2000F 1HR 0G, B -100F 0.5HR 500F 2+2HR	3.00	R.T.	169.0	3.5 PCT NAACL	1.500	0.480	CANT*	200.00	105.00*			1969 76136
2000F 1HR 0G, B -100F 0.5HR 700F 2+2 HR	3.00	R.T.	180.0	3.5 PCT NAACL	1.500	0.480	CANT*	160.00	50.00			1969 76136
2000F 1HR 0G, B -100F 0.5HR 800F 2+2 HR	3.00	R.T.	207.0	3.5 PCT NAACL	1.500	0.480	CANT*	70.00	40.00			1969 76136
2000F 1HR 0G, B -100F 0.5HR 900F 2+2 HR	3.00	R.T.	214.0	3.5 PCT NAACL	1.500	0.480	CANT*	56.00	35.00			1969 76136
2000F 1HR 0G, B -100F 0.5HR 1100F 2+2 HR	3.00	R.T.	221.0	3.5 PCT NAACL	1.500	0.480	CANT*	43.00	10.00			1969 76136

*Note - Data which do not meet minimum specimen thickness requirements of 2.5(KISCC/TYS) squared.

+Note - (*=SG) in design column implies that Asterisked specimens are side-grooved (SG).

Figure 1.16. Format for Stress Corrosion Cracking Threshold Data; Example Taken from Table 3.2.3.2, AFC 77 Stainless Steel Alloy.

Greater than (>) and less than (<) signs before the K_{ISCC} value indicates that the actual value is either greater than or less than the value stated, respectively. Data containing these signs were considered to be informative since little data exists and so were included; however, the data were not considered definitive and so were excluded from mean and standard deviation values.

CHAPTER 2
METHODS OF CALCULATIONS

2.0	OVERVIEW	2-1
2.1	PLANE-STRAIN FRACTURE TOUGHNESS (K_{Ic})	2-18
2.2	CRITICAL PLANE STRESS FRACTURE TOUGHNESS	2-22
2.3	THE APPARENT FRACTURE TOUGHNESS	2-26
2.4	R-CURVE (K_R VERSUS Δa_{eff})	2-28
2.5	FATIGUE CRACK GROWTH RATE	2-30
2.6	SUSTAINED-LOAD CRACK GROWTH RATES	2-41
2.7	THRESHOLD STRESS INTENSITY (K_{Isc})	2-43

CHAPTER 2
METHODS OF CALCULATIONS

TABLE OF CONTENTS

<u>SECTION</u>		<u>PAGE</u>
2.0	OVERVIEW	2-1
	2.0.1 <u>Data Review and Acceptance Criteria</u>	2-1
	2.0.2 <u>Fracture Mechanics Basis</u>	2-4
	2.0.3 <u>Test Specimen Geometries</u>	2-5
2.1	PLANE-STRAIN FRACTURE TOUGHNESS (K_{Ic})	2-18
2.2	CRITICAL PLANE STRESS FRACTURE TOUGHNESS	2-22
	2.2.1 <u>Plane Stress and Transitional Fracture Toughness</u>	2-22
	2.2.2 <u>Plane Stress and Transitional Fracture Toughness Testing</u>	2-23
	2.2.3 <u>Critical Stress-Intensity Factor (K_C)</u>	2-25
2.3	THE APPARENT FRACTURE TOUGHNESS	2-26
2.4	R-CURVE (K_R VERSUS Δa_{eff})	2-28
2.5	FATIGUE CRACK GROWTH RATE	2-30
	2.5.1 <u>Fatigue Crack Growth Behavior</u>	2-30
	2.5.2 <u>Data Acceptance Criteria</u>	2-32
	2.5.3 <u>Data Reduction Procedures</u>	2-32
	2.5.4 <u>Data Reporting Procedures</u>	2-34
2.6	SUSTAINED-LOAD CRACK GROWTH RATES	2-41
	2.6.1 <u>Sustained-Load Crack Growth Rate Behavior</u>	2-41
	2.6.2 <u>Data Acceptance Criteria</u>	2-42
	2.6.3 <u>Data Reduction Procedures</u>	2-43
	2.6.4 <u>Data Reporting Procedures</u>	2-43
2.7	THRESHOLD STRESS INTENSITY (K_{Isc})	2-43
	2.7.1 <u>The Threshold</u>	2-43
	2.7.2 <u>Conditions for Validity of Data</u>	2-46

CHAPTER 2
LIST OF ILLUSTRATIONS

<u>FIGURE</u>		<u>PAGE</u>
2-1	Center Cracked Panel (CCP) Specimen.	2-8
2-2	Compact Tension (CT) Specimen.	2-8
2-3	Three Point Notched Bend (NB) Specimen.	2-9
2-4	Four Point Notched Bend (4-NB) Specimen.	2-9
2-5	Cantilever Beam (CANT) Specimen.	2-9
2-6	Dimensions of Several T Type Wedge Opening Load (WOL) Specimens.	2-10
2-7	Modified 1-T WOL (BWOL) Specimen Used to Determine K_{Isc} by Bolt Loading.	2-11
2-8	Single Edge Notch Tensile (SENT) Specimen.	2-11
2-9	Typical Design for Part-Through-Surface-Crack (PTSC) Specimen.	2-11
2-10	K_B Bar (KB-BAR) Specimen	2-12
2-11	Double Cantilever Beam (DCB) Specimen with Side Grooves.	2-12
2-12	Bolt-Loaded Double Cantilever Beam (BDCB) Specimen.	2-13
2-13	Typical Tapered Double Cantilever Beam (TDCB) Specimen with Side Grooves.	2-13
2-14	Center-Notch Tensile (CNT) Specimen.	2-13
2-15	Fracture Toughness Behavior as a Function of Thickness.	2-19
2-16	Typical Crack Growth Behavior in Plane Stress and Transitional Stress States.	2-24
2-17	Thin-Section, Center-Cracked Tension Panel Configuration.	2-24
2-18	Description of the Three Fracture Toughness Criteria that are Utilized to Estimate Residual Strength Under Tearing Fracture Conditions.	2-27

CHAPTER 2
LIST OF ILLUSTRATIONS
(Continued)

<u>FIGURE</u>		<u>PAGE</u>
2-19	Typical Crack Growth-Life Curve.	2-31
2-20	A Cubic Spline Curve Fit to FCGR Data for 2219-T851 Aluminum at a Stress Ratio of 0.3.	2-36
2-21	Schematic Drawing of Fatigue Cracked Cantilever Beam Test Specimen and Fixtures.	2-45

CHAPTER 2
LIST OF TABLES

<u>TABLE</u>		<u>PAGE</u>
2.1	APPLICABLE LIST OF STANDARDS FOUND IN PART 10, THE ASTM BOOK OF STANDARDS (1982)	2-2
2.2	CORRELATION LISTING OF TEST SPECIMEN SYMBOL, TEST SPECIMEN GEOMETRY, AND REFERENCE FIGURE NUMBER	2-7
2.3	STRESS-INTENSITY FACTOR COEFFICIENTS FOR TEST SPECIMEN GEOMETRIES USED TO GENERATE DAMAGE TOLERANT DATA	2-14
2.4	CRITERIA CHECKS FOR FATIGUE CRACK GROWTH RATE DATA	2-33
2.5	EXAMPLE FATIGUE CRACK GROWTH RATE TABLE (2219-T851 ALUMINUM)	2-38
2.6	FULL INTERVAL COMPARISONS OF LIFE PREDICTION RATIOS	2-40

CHAPTER 2

METHODS OF CALCULATIONS

2.0 OVERVIEW

This chapter briefly describes the methods used to calculate the damage tolerant properties reported in the Handbook. The properties reported for characterizing fracture resistance include:

- K_{IC} , the plane-strain fracture toughness
- K_C , the critical plane-stress (or transitional) fracture toughness
- K_{App} , the apparent plane-stress fracture toughness
- K_R , the tearing resistance

and, the properties reported for characterizing subcritical crack growth resistance include:

- $\frac{da}{dN}$, the constant amplitude fatigue crack growth rate
- $\frac{da}{dt}$, the sustained-load crack growth rate
- K_{Isc} , the threshold for sustained load cracking

Sections 2.1 through 2.7 describe these properties and the specific methods of calculations utilized to convert laboratory (specimen) data into the properties reported.

2.0.1 Data Review and Acceptance Criteria

Newly acquired data and data available from previous revisions of the Handbook were systematically reviewed and analyzed. The principal data acceptance criteria were based on criteria established by the American Society for Testing and Materials (ASTM); these criteria are embedded within ASTM standards for test methods and practices. Table 2.1 lists those standards used to provide criteria for plane-strain fracture toughness (K_{IC}) data, for R-curve data, and for fatigue crack growth rate (da/dN) data. ASTM literature

TABLE 2.1
APPLICABLE LIST OF STANDARDS FOUND IN PART 10,
THE ASTM BOOK OF STANDARDS (1982)

<u>ASTM STD</u>	<u>TITLE</u>
E616-81	Standard Terminology Relating to Fracture Testing
E399-81	Test Method for Plane-Strain Fracture Toughness of Metallic Materials
E561-81	Practice for R-Curve Determination
E647-81	Test Method for Constant-Load-Amplitude Fatigue Crack Growth Rates Above 10^{-8} m/Cycle

was also reviewed to establish criteria based on typical engineering practice for the other types of data collected and reported.

Newly acquired data was substantially easier to process than the data available from previous revisions since the data suppliers screened their data according to ASTM criteria before it was released to the data processing organization (UDRI). Also, when questions concerning newly acquired data developed, the suppliers could be called and the questions resolved.

For the case of previously available Handbook data, it was necessary to systematically review the data employing a multi-step process. First, the computer compatible input data (computer cards) supplied to UDRI by MCIC were compared to the data reported in the 1975 revision of the Handbook. When discrepancies between variables (such as stress ratio, frequency, specimen direction, etc) were found, they were marked with an asterisk on the card image data so that the differences could be investigated further. One means of settling the discrepancy was through use of the second step in the process whereby the data were compared to the original reference. Since the data on the computer cards listed the specimen identification number, the original data was normally found with relative ease and comparisons made. Every attempt was made to consult the original references and verify the accuracy of these available data. As with newly acquired data, available data were also reviewed relative to applicable ASTM criteria prior to being identified as candidate data for the 1983 revision.

The final step in the review process was the determination of whether the data were a "true" representation of the behavior they described. This step was implemented for both newly acquired data as well as for the available Handbook data in order to eliminate suspect data through subjective criteria. Unfortunately, it is not possible to detail the subjective criteria that were employed to exclude questionable data. It can be stated that the principal mode of operation here was by way of comparison between behaviors that were expected to be somewhat similar.

2.0.2 Fracture Mechanics Basis

The damage tolerant data reported in this Handbook utilize the technology of linear elastic fracture mechanics. This technology is widely applied throughout the aerospace industry to relate structural calculations for cracked structures to material behavior in the presence of cracks. In essence, fracture mechanics provides a structural parameter, the stress-intensity factor (symbol K) which characterizes the magnitude of stresses and strains in the crack tip region of essentially elastic structures. It was postulated that the stress-intensity factor represents a similitude parameter that describes crack tip behavior under various loading conditions (monotonically increasing load, fatigue loading, etc.); the hypothesis has been verified for a wide number of materials, loading conditions, and failure type mechanisms. For a more thorough review of linear elastic fracture mechanics and its applications to the aerospace industry, see AFWAL-TR-82-3073, USAF Damage Tolerant Design Handbook: Guidelines for the Analysis and Design of Damage Tolerant Aircraft Structures.

Currently, there are developments that are extending the technology of fracture mechanics to aid in the solution of crack problems for which the assumptions of linear elastic fracture mechanics are invalid. This technology is referred to as nonlinear fracture mechanics and its similitude parameter is the J-integral (J), or alternately the crack tip opening displacement (δ). To date, nonlinear fracture mechanics has been successfully utilized to characterize tearing type fractures and fractures occurring in the presence of large-scale yielding. Some evidence has been presented suggesting that J may provide a similitude parameter for non-monotonically increasing type loadings, i.e., for fatigue loadings; but, questions still exist here. It is expected that subsequent revisions of this Handbook will include nonlinear fracture mechanics type data such as J_{IC} , a plane-strain fracture toughness property, and J_R -curves, (tearing resistance curves).

2.0.3 Test Specimen Geometries

As described above, the stress-intensity factor provides a parameter that can be used to establish similitude between two cracked structures. This means that if the stress-intensity factor in structure no. 1 equals the stress-intensity factor in structure no. 2 and if other conditions (loading, material, environment, etc) are the same, then the cracks in both structures will behave the same way. This concept provides the justification for conducting material behavior studies on small laboratory test specimens (coupons) which contain cracks. If the resistance to cracking in the laboratory can be optimized by a choice of material, then improved resistance can also be obtained for structural hardware (given that the material can be fabricated into the hardware without processing degradation taking place).

The types of test specimen geometries that have been employed to generate damage tolerance (fracture mechanics) type data for this Handbook are summarized in Table 2.2. Table 2.2 also guides the reader to individual figures (Figures 2.1 through 2.14) which describe the geometries associated with individual specimen names and symbols.

To relate the crack type data collected in a cracked test specimen to other cracked structures, it is necessary to have a description of the stress-intensity factor (K) as a function of crack length (a) for the test specimen geometry. Over the last fifteen years, a great deal of attention has been given to generating accurate stress-intensity factor equations for laboratory test specimen geometries, due to their importance to standard methods of test and to reporting data. The stress-intensity factor equations are typically presented in either of the following two forms:

$$K = \sigma \sqrt{\pi a} \cdot \beta$$

where σ = remote stress (load \div area) (2.1)
 a = crack length measure
 β = function of crack length and global geometry

or

$$K = \frac{P}{BW^{\frac{1}{2}}} Y \quad (2.2)$$

where

P = load

B = thickness of specimen

W = width of specimen

Y = function of crack length (a)
and global geometry

Equation 2.1 is used when the loading is applied remotely from the crack, whereas Equation 2.2 is more typically used for point loading or localized loading conditions. One should note that K is a linear function of loading (σ in Equation 2.1 and P in Equation 2.2) and that the loading and geometric components of the equations are independent of each other. Thus, if one wishes to describe a stress-intensity factor relationship for a given geometry, they might formulate the equations in the following forms:

$$\frac{K}{\sigma} = \sqrt{\pi a} \cdot \beta \quad (2.3)$$

or

$$\frac{\frac{K}{P}}{BW^{\frac{1}{2}}} = Y \quad (2.4)$$

Equations 2.3 and 2.4 are referred to as stress-intensity factor coefficients; the right hand side of these equations only describes the effect of the crack in the given geometry.

Table 2.3 provides a listing of stress-intensity factor coefficients which were used to generate data for this Handbook. Each equation is given a stress-intensity factor equation number, e.g. SIF.7 refers to the stress-intensity factor coefficient for the WOL (Wedge Opening Load) specimen geometry illustrated in Figure 2.6. Also note that Table 2.3 has a remarks section which describes the conditions under which individual equations were used.

TABLE 2.2
CORRELATION LISTING OF TEST SPECIMEN SYMBOL,
TEST SPECIMEN GEOMETRY, AND REFERENCE FIGURE NUMBER

SYMBOL	TEST SPECIMEN	GEOMETRY DESCRIBED IN FIGURE NUMBER
CCP	Center Crack Panel	2.1
CT	Compact (Tension)	2.2
NB	Three Point Notched Bend	2.3
4-NB	Four Point Notched Bend	2.4
CANT	Cantilever Beam	2.5
WOL	Wedge Opening Load	2.6
BWOL	Bolt Loaded WOL	2.7
SENT	Single Edge Notch Tension	2.8
PTSC	Part-Through Surface Crack	2.9
KB-BAR	K_B BAR	2.10
DCB	Double Cantilever Beam	2.11
BDCB	Bolt Loaded DCB	2.12
TDCB	Tapered Double Cantilever Beam	2.13
CNT	Center Notch Tension	2.14

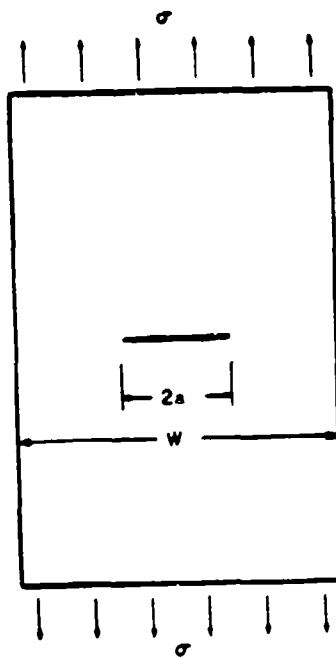


Figure 2.1. Center Cracked Panel (CCP) Specimen.

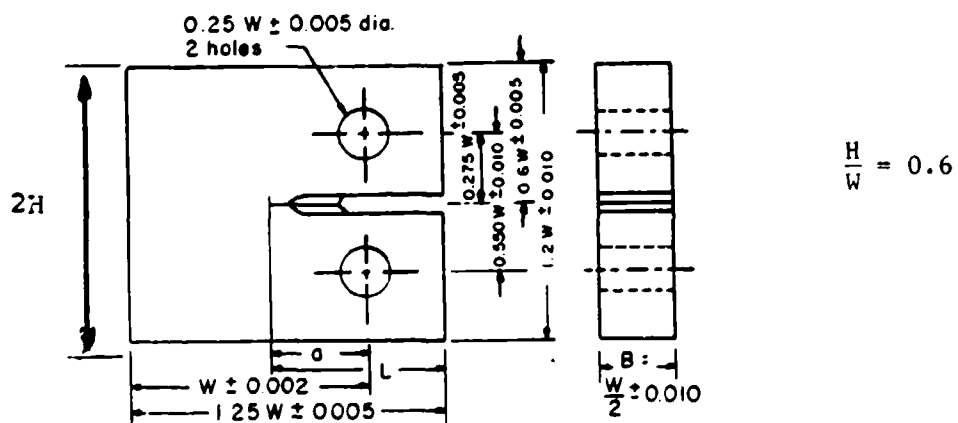


Figure 2.2. Compact Tension (CT) Specimen.

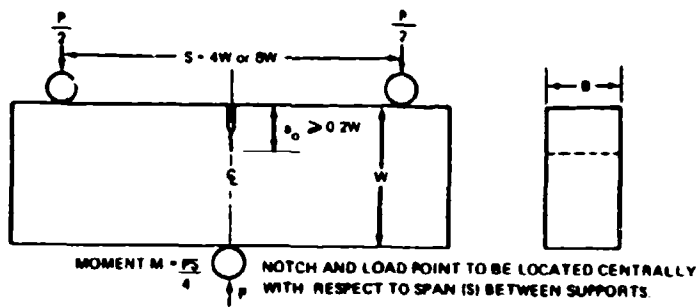


Figure 2.3. Three Point Notched Bend (NB) Specimen.

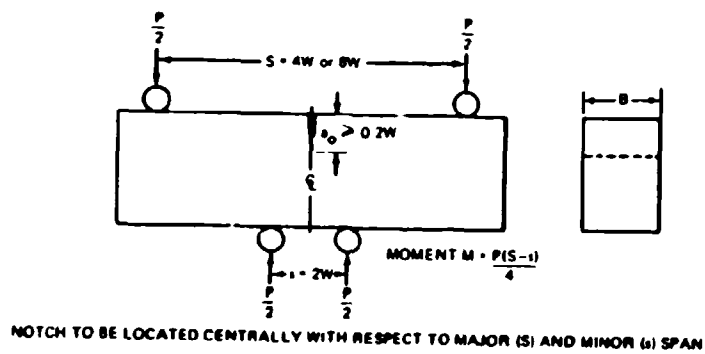


Figure 2.4. Four Point Notched Bend (4-NB) Specimen.


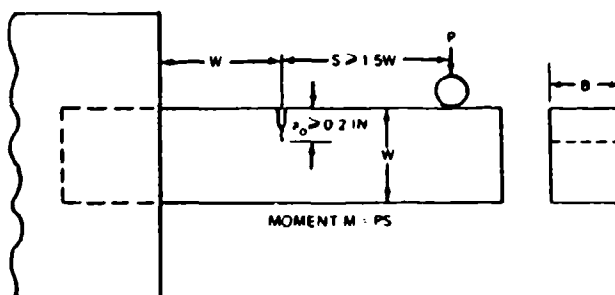


Figure 2.5. Cantilever Beam (CANT) Specimen.

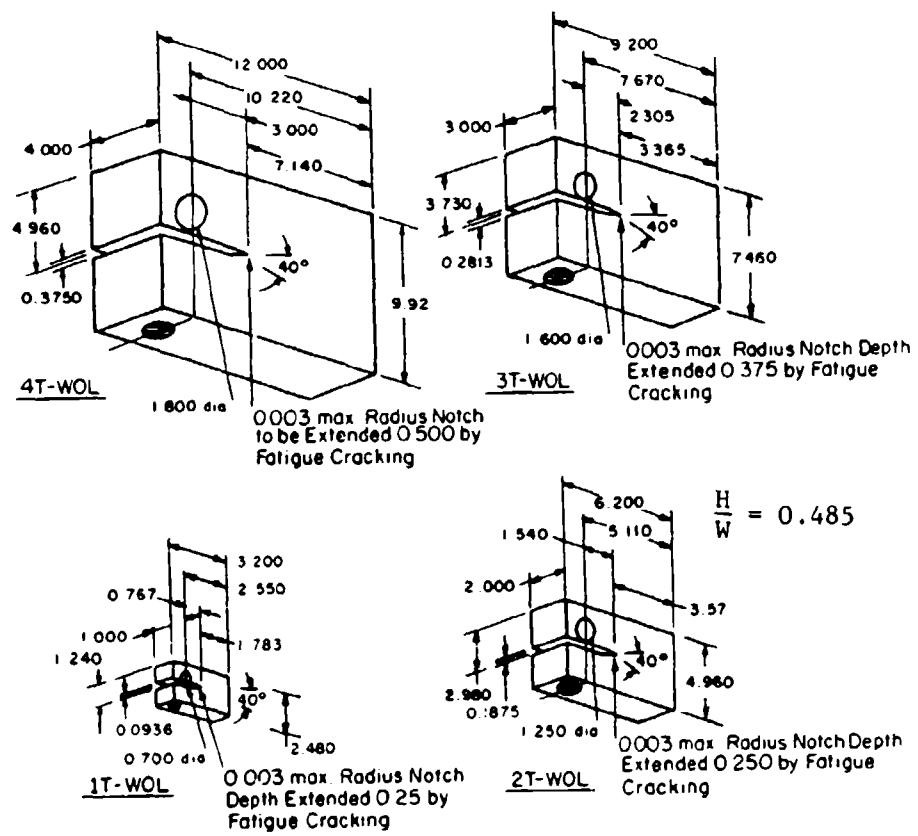

Note:
All Dimensions are in Inches.

Figure 2.6. Dimensions of Several T Type Wedge Opening Load (WOL) Specimens.

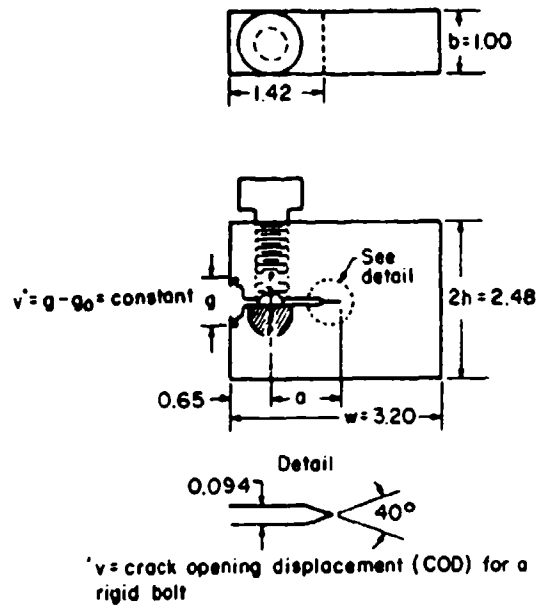


Figure 2.7 Modified 1-T WOL (BWOL) Specimen Used to Determine K_{Isc} by Bolt Loading.

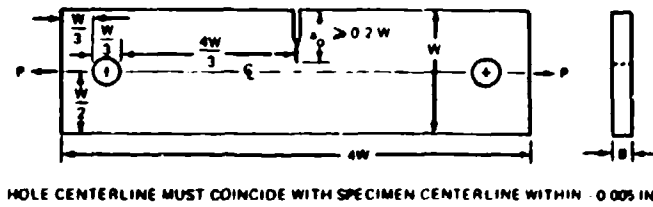


Figure 2.8. Single Edge Notch Tensile (SENT) Specimen.


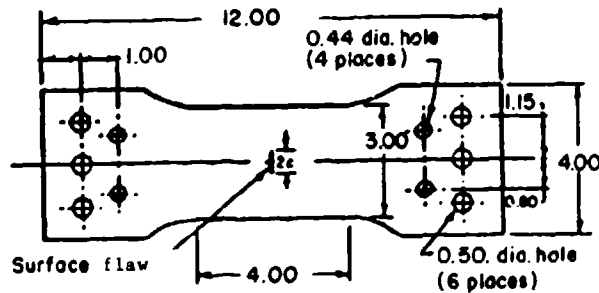


Figure 2.9. Typical Design for Part-Through-Surface-Crack (PTSC) Specimen.

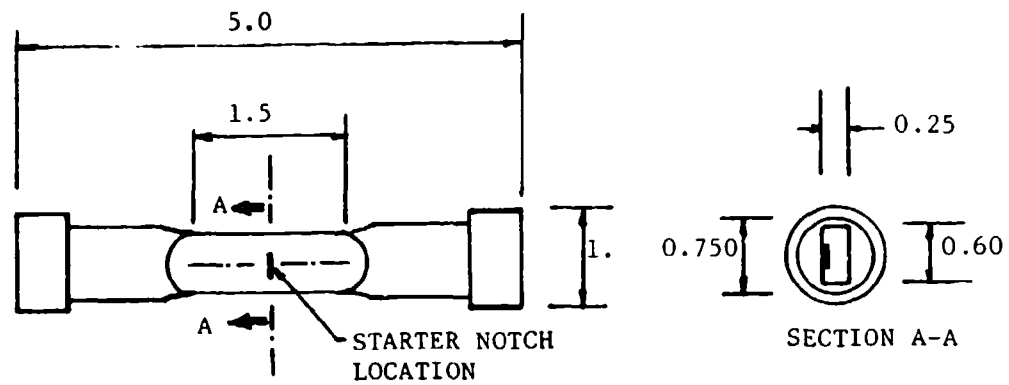

ALL DIMENSIONS IN INCHES

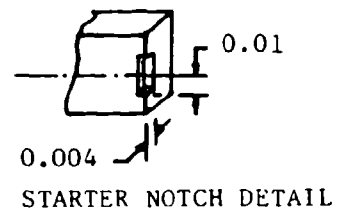


Figure 2.10. K_B Bar (KB-BAR) Specimen.

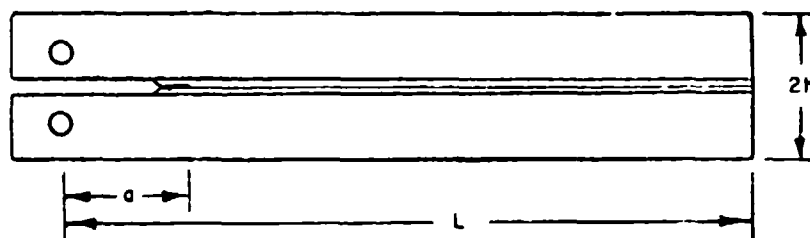


Figure 2.11. Double Cantilever Beam (DCB) Specimen with Side Grooves.

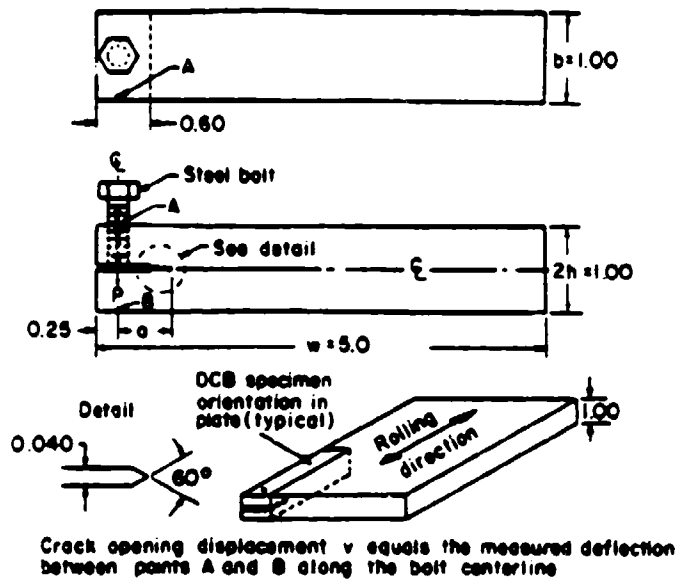


Figure 2.12. Bolt-Loaded Double Cantilever Beam (BDCB) Specimen.

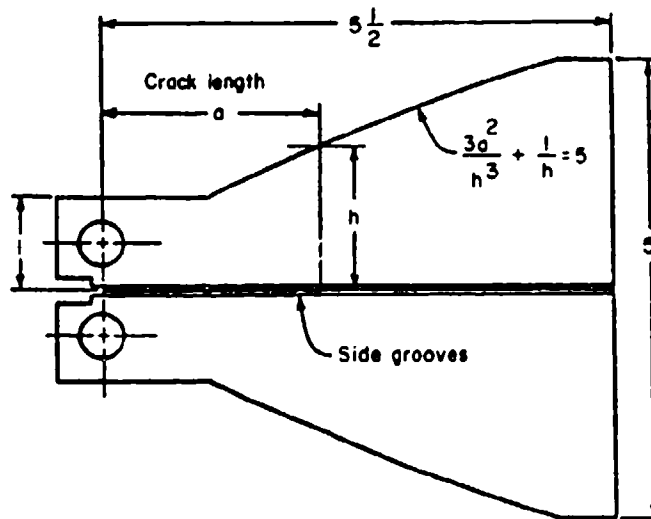


Figure 2.13. Typical Tapered Double Cantilever Beam (TDCB) Specimen with Side Grooves.

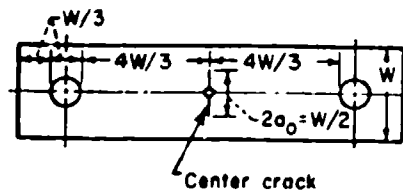


Figure 2.14. Center-Notch Tensile (CNT) Specimen.

TABLE 2.3
STRESS-INTENSITY FACTOR COEFFICIENTS FOR TEST SPECIMEN
GEOMETRIES USED TO GENERATE DAMAGE TOLERANT DATA

TEST SPECIMEN GEOMETRY	STRESS-INTENSITY FACTOR COEFFICIENT	EQUATION NUMBER	REMARKS
CCP (See Figure 2.1)	$\frac{K}{\sigma} = \sqrt{\pi a} \cdot (\text{Sec } \alpha a)^b$ $\alpha = a/W$	SIF.1	This equation was used whenever K was calculated for the CCP Specimen
CT (See Figure 2.2)	$\frac{K}{\sigma} = \frac{(2+a)}{8W^2} \cdot [0.866 + 4.64a - (2-a)^{3/2} - 13.32a^2 + 14.72a^3 - 5.6a^4]$ $\frac{a}{H} = \frac{a}{W}$ $\frac{H}{W} = 0.600$	SIF.2	This equation was used whenever K was calculated for data generated with the CT specimen; the equation is valid for $a/W > 0.2$
CT (See Figure 2.2)	$\frac{K}{\sigma} = \frac{a^2}{8W^2} [29.6 - 185.5a + 655.7a^2 - 1017a^3 + 638.9a^4]$ $\alpha = a/W$ $\frac{H}{W} = 0.600$	SIF.3	This equation was used to calculate K for data incorporated into pre-1983 revisions. Reprocessed a vs N data utilized equation SIF.2
NB (J PI BEND) (See Figure 2.3)	$\frac{K}{\sigma} = \frac{S a^2}{8W^2} [2.9 - 4.6a + 21.8a^2 - 37.6a^3 + 38.7a^4]$ $\alpha = a/W$ $S = \text{span length}$	SIF.4	No new data were processed from NB specimens. Previous data incorporated into the handbook utilized this equation.

TABLE 2.3 (Continued)

STRESS-INTENSITY FACTOR COEFFICIENTS FOR TEST SPECIMEN GEOMETRIES USED TO GENERATE DAMAGE TOLERANT DATA

TEST SPECIMEN GEOMETRY	STRESS-INTENSITY FACTOR COEFFICIENT	EQUATION NUMBER	REMARKS
4-NB (4 PT BEND)	$\frac{K}{P} = \frac{3}{8W} \left[1.99 - 2.47a + 12.97a^2 - 23.17a^3 + 26.80a^4 \right]$	SIF.5	No new data were processed from 4-NB specimens. Previous data incorporated into the handbook utilized this equation. s/W must be greater than 2.
(See Figure 2.4)	$a = a/W$ $M = P(S-s)/6, \text{ moment}$ $S, s = \text{major and minor span}$		
CANT	$\frac{K}{P} = 4.12 \left[(1-a)^{3/2} - (1-a) \right]^{1/2}$	SIF.6	No new data were processed from CANT specimens. Previous data incorporated into the handbook utilized this equation.
(See Figure 2.5)	$a = a/W$ $M = P \times S, \text{ moment}$		
WOL	$\frac{K}{P} = \frac{(2+s)}{(1-a)^{3/2}} \left[\begin{array}{l} 0.8072 + 8.858s \\ -30.23a^2 + 41.088a^3 \\ -24.15a^4 + 4.951a^5 \end{array} \right]$	SIF.7	All new a vs N data from WOL specimens with H = 0.485 were processed using this equation
(See Figure 2.6)	$a = a/W$ $H = 0.485$		
BMOL	$\frac{K}{P} = \frac{3}{8W} \left[\begin{array}{l} 30.96 - 195.8a + 730.6a^2 \\ -1186.3a^3 + 754.6a^4 \end{array} \right]$	SIF.8	Equation was used to calculate stress-intensity factors for both WOL and BMOL in prc-1983 revisions. No new BMOL raw data were received for processing.
(See Figure 2.7)	$a = a/W$ $B = \sqrt{B \cdot B_N}$ $B_N = \text{Net Thickness at Side Groove}$		

TABLE 2.3 (Continued)

STRESS-INTENSITY FACTOR COEFFICIENTS FOR TEST SPECIMEN GEOMETRIES USED TO GENERATE DAMAGE TOLERANT DATA

	STRESS-INTENSITY FACTOR COEFFICIENT	EQUATION NUMBER	REMARKS
SENT (See Figure 2.8)	$\frac{K}{P} = \frac{a^2 b}{8W^2} [1.99 - 0.4124a + 18.70a^2 - 38.48a^3 + 53.85a^4]$ $u = a/W$	SIF.9	New da/dN data processed from SENT specimens utilized this equation. Previous data incorporated into handbook also utilized this equation.
PTSC (See Figure 2.9)	$\frac{K}{Q} = 1.1 \left(\frac{na}{Q} \right)^{1/2}$ <p>where for $(a/c) \leq 1$</p> $Q = 1.0 + 1.464 \left(\frac{a}{c} \right)^{1.65}$ <p>a = depth 2c = surface length</p>	SIF.10	Equation was used to reduce a vs N data for PTSC specimens. Previous data incorporated into handbook also used a similar version of this equation.
KB 6AK (See Figure 2.10)	Equation used by Aircraft Engine Group of General Electric Company. Closely Approximates Newman and Raju Solution Presented in AFMAL-TR-82-3073	SIF.11	Used for da/dN testing. Data received was directly incorporated into the 1983 revision for this geometry.
DCB (See Figure 2.11)	$\frac{K}{P} = \frac{b^2 Y}{8W^2}$ $u = a/W$ $Y = Y(a/W, H/W)$ $B = \sqrt{B_N}$ $B_N = \text{Net Thickness at Side Groove}$	SIF.12	Specimen used for generating da/dN, da/dt, and K _{I,DCB} data in pre-1983 revisions. The function Y was specified for given H/W. Data collected with DCB specimens were not reprocessed and no new data were received.

TABLE 2.3 (Concluded)

STRESS-INTENSITY FACTOR COEFFICIENTS FOR TEST SPECIMEN GEOMETRIES USED TO GENERATE DAMAGE TOLERANT DATA

TEST SPECIMEN GEOMETRY	STRESS-INTENSITY FACTOR COEFFICIENT	EQUATION NUMBER	REMARKS
B-DGB (See Figure 2.12)	$K = \frac{\sqrt{Eh}}{4} \left[\frac{3h}{(a+0.6h)^2 + h^2} \right]^{1/2}$	SIF.13	Used for K1acc testing. Data previously calculated using this equation were directly incorporated into the 1983 revision.
TDCB (See Figure 2.13)	$K = \left[\frac{E}{2B} \left(\frac{dc}{da} \right)^2 \right]^{1/2}$ where $\frac{dc}{da} = 1.65 - 0.925 \left(0.8 - \frac{B_N}{B} \right) \cdot 10^{-6} / 1b$ B_N = Net Thickness at Side Groove E = Elastic Modulus ν = Poisson's Ratio	SIF.14	Equation used by McDonnell Aircraft Company to reduce data referenced in Ref. no. 84360 (Equation is based on Plane-Strain Assumptions). Data were incorporated without change.
DDCB (See Figure 2.13)	$K = \left[\frac{E}{2B} \left(\frac{dc}{da} \right)^2 \right]^{1/2}$ where $\frac{dc}{da}$ = constant E = Elastic Modulus $B = \sqrt{B \cdot B_N}$ B_N = Net Thickness at Side Groove	SIF.15	No new data were processed from TDCB specimens. Previous data incorporated into the handbook utilized this equation.
CN1 (See Figure 2.14)	$K = \sqrt{Eh} \left[1 - 0.2a + 4a^2 \right]^{1/2}$ $1 \leq a/w$ SIF.16 is comparable to SIF.1 FOR $0 < a < 0.3$	SIF.16	No new data were processed from CN1 specimens. Previous data (K1acc) for sheet materials) incorporated into the handbook utilized this equation.

2.1 PLANE-STRAIN FRACTURE TOUGHNESS (K_{IC})

The plane-strain fracture toughness (K_{IC}) property was initially established to characterize the fracture resistance of materials that exhibited rather abrupt fractures in the presence of cracks. Early observations showed that thickness had a pronounced effect on the critical levels of stress-intensity factor associated with fracture; a schematic illustrating this behavior is presented in Figure 2.15. As noted in the schematic, for thicknesses greater than the experimentally determined lower-bound, the critical stress-intensity factor level was found to be relatively constant.

The reasons for the independence of toughness with further increases in thickness were related to the amount and type of yielding which could occur at the crack tip under what has been referred to as plane-strain conditions. Because the thickness-independent toughness property was useful for comparing a large variety of metals for fracture resistance, ASTM (American Society for Testing and Materials) embarked on a standardization effort that eventually resulted in the ASTM Standard Test Method for plane-strain fracture toughness of metallic materials, i.e., in the ASTM Standard E399.

The ASTM Standard E399 is the current procedure for determining critical plane-strain stress intensity factors (K_{IC} values) for high-strength alloys. From the method of test, "The property K_{IC} determined by this method characterizes the resistance of a material to fracture in a neutral environment in the presence of a sharp crack under severe tensile constraint, such that the state of stress near the crack front approaches tritensile plane-strain, and the crack-tip plastic region is small compared with the crack size and specimen dimensions in the constraint direction."

Assuming that plane-strain conditions are approximated when unstable cracking occurs at the crack front during a K_{IC} test, the critical stress intensity factor calculated from the

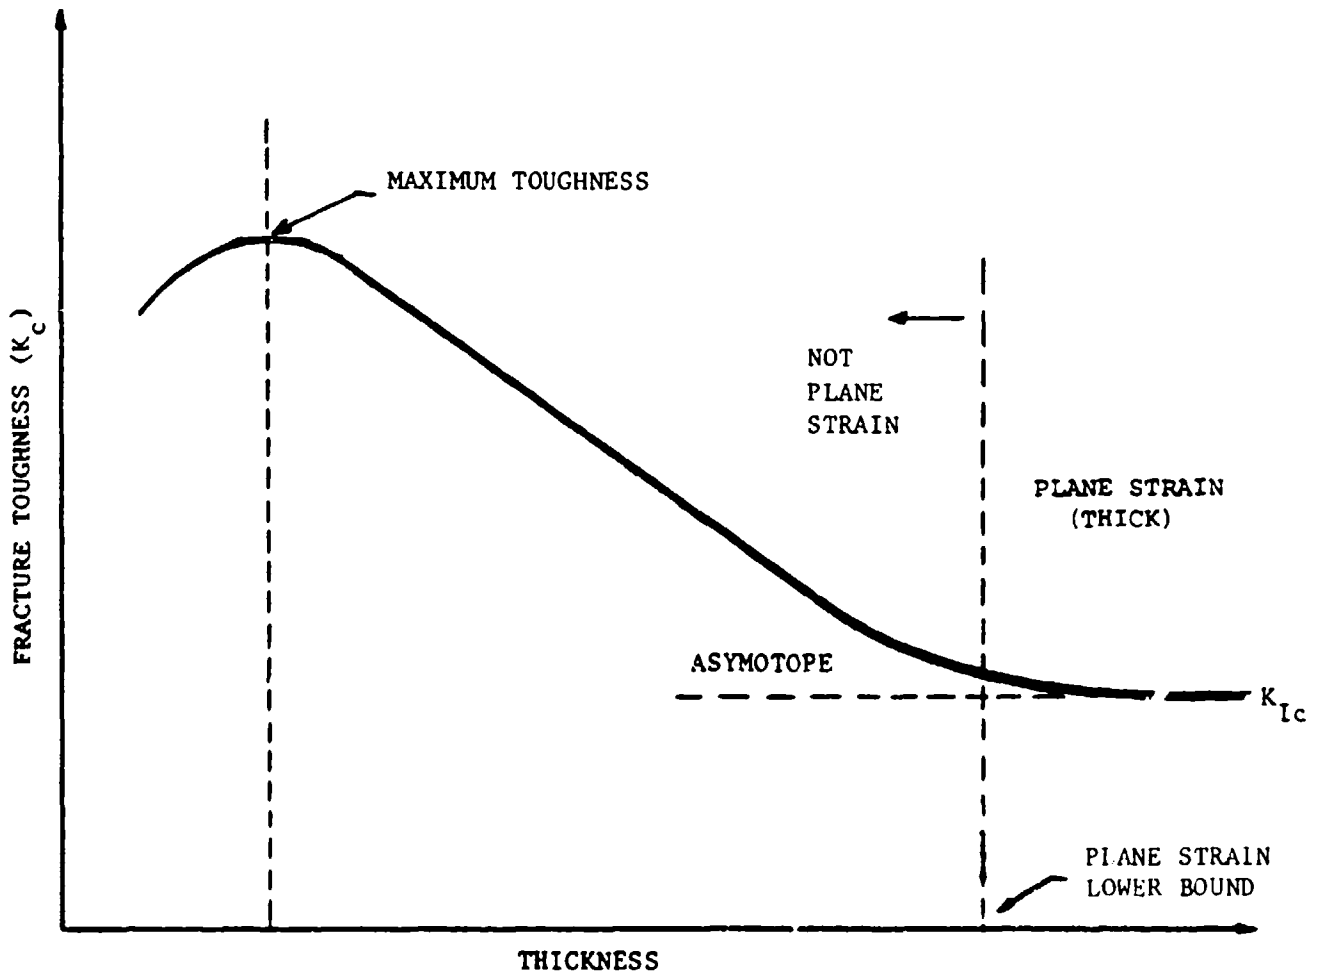


Figure 2.15. Fracture Toughness Behavior as a Function of Thickness.

test data is characteristic of the material of the specimen at the testing temperature and for the specific crack growth direction. Since the properties vary somewhat from specimen to specimen in one plate or in one heat, and from heat to heat of a given alloy type with the same heat treatment, the measured K_{IC} values for several heats will show some degree of scattering in the data. Usually, the extent of scattering is greater than that for replicate tensile tests. For this reason, a relatively large number of data points would be required to establish minimum design values for any of the fracture mechanics parameters. To minimize the scatter in data, maximum effort is required in controlling the processing, preparation, and testing of each specimen. These precautions are discussed in the Method of Test (ASTM E399).

The ASTM E399 procedure indicates that calculated K values be designated K_Q , which is a provisional value. When the validity of the results is established by the procedures designated in the Method of Test, then the K_Q value can be identified as a valid K_{IC} value. Some of the primary criteria for judging the validity of K_{IC} values are based on crack length and specimen thickness conditions. The test data must demonstrate that sufficient constraint was available to justify the plane-strain assumptions. The other requirements for validity of the K_{IC} values involve measurements of the length of the fatigue crack, contour of the crack front, out-of-plane deviation of the fatigue crack, maximum stress intensity resulting from the fatigue cracking load, and details of the load-deformation curves.

All newly acquired plane-strain fracture toughness (K_{IC}) data incorporated in the 1983 Handbook revision were generated using the ASTM Standard E399. These newly acquired data were generated using the CT specimen geometry (See Figure 2.2). All suppliers of new K_{IC} data provided only E399 validated K_{IC} data in a reduced format which facilitated direct incorporation into

the Handbook. Data incorporated in earlier revisions for the most part utilized ASTM Standard E399 or the predecessor tentative method for plane-strain fracture toughness testing; and after review, these data were also included into the 1983 revision. In some instances, nonstandard specimens were used for generating critical plane-strain stress-intensity factors in the earlier revisions. Some of these data were incorporated in the 1983 revision on the basis that a reasonable procedure was used and that corresponding data from other sources were limited for the alloys concerned. All data were checked against the criteria for specimen thickness (B) and crack length (a), i.e., $B, a \geq 2.5 (K_{IC}/\sigma_{ys})^2$ where σ_{ys} is the tensile yield strength.

2.2 CRITICAL PLANE STRESS FRACTURE TOUGHNESS

2.2.1 Plane Stress and Transitional Fracture Toughness

The critical level of the stress-intensity factor for non-plane-strain conditions is normally described with the symbol K_{IC} , see Figure 2.15, and is referred to as the plane-stress or transitional fracture toughness. Generally, plane-stress fracture-toughness testing is representative only of through-the-thickness cracks in relatively thin section materials. For a given material thickness, this configuration has the least lateral restraint on the crack front and, hence, approaches most closely the ideal plane-stress stress state conditions at the crack tip. As the material thickness increases, transitional stress state behavior is introduced by the restraint of additional material along the crack front. In contrast to that in plane-strain fracture-toughness testing, the characterization of fracture toughness in the plane-stress and transitional-stress states is complicated by the degree to which crack tip plasticity and associated stable crack extension are manifested prior to fracture. Although an explicit test method for this mode of toughness has not been formulated, there are a number of useful experimental guidelines which have been developed.

As background information, the nature of plane-stress and transitional fracture toughness is described here in terms of its deviation from that of the plane-strain stress state. Current procedures for this mode of testing and the associated analytical formulations of toughness then are presented.

The difficulties that beset the characterization of plane stress and transitional fracture are not only of a theoretical nature, but also of a practical experimental nature. Basic questions on the nature of plasticity, crack extension, and crack instability, as well as the wide variation in experimental techniques among laboratories all contribute to variability in the resulting fracture toughness evaluations. However, in spite of these difficulties, surprisingly consistent characterizations of fracture behavior can be obtained.

During the fracture test of a structural material in a plane-stress or transitional-stress state, stable extension of the initial fatigue precrack may occur as the load increases. This behavior is illustrated schematically in the crack growth curve of Figure 2.16. Depending on the material, stable crack extension may amount to 30 percent or more of the initial precrack length.

Once it is realized that fracture under these conditions is not an abrupt instability instantaneously associated with a small increment of crack extension, it must also be recognized that a single toughness parameter is not sufficient to characterize this complex behavior. In fact, the concept of crack growth resistance curves (see Section 2.4) is an outgrowth of these observations and best describes the material behavior. However, as a means of characterizing fracture behavior in plane-stress and transitional stress state, engineers have traditionally utilized abrupt fracture concepts, i.e., have used critical stress-intensity factor levels, to describe various events associated with the observed behavior.

2.2.2 Plane Stress and Transitional Fracture Toughness Testing

The procedures associated with testing thin-section center-cracked tension panels differ from those associated with plane-strain fracture toughness testing only in the additional emphasis and refinement that is directed to monitoring the slow, stable tear portion of the fracture process.

The general testing configuration is illustrated schematically in Figure 2.17. The specimen with an initial fatigue precrack, $2a_0$, is loaded slowly under load or stroke control. The onset and extension of crack growth under increasing load is usually monitored photographically, visually, or by means of compliance gage calibration until fracture occurs.

Although, as previously mentioned, more attention is currently being directed to monitoring the detail stress and crack length dimensions during the slow tear process, the preponderance

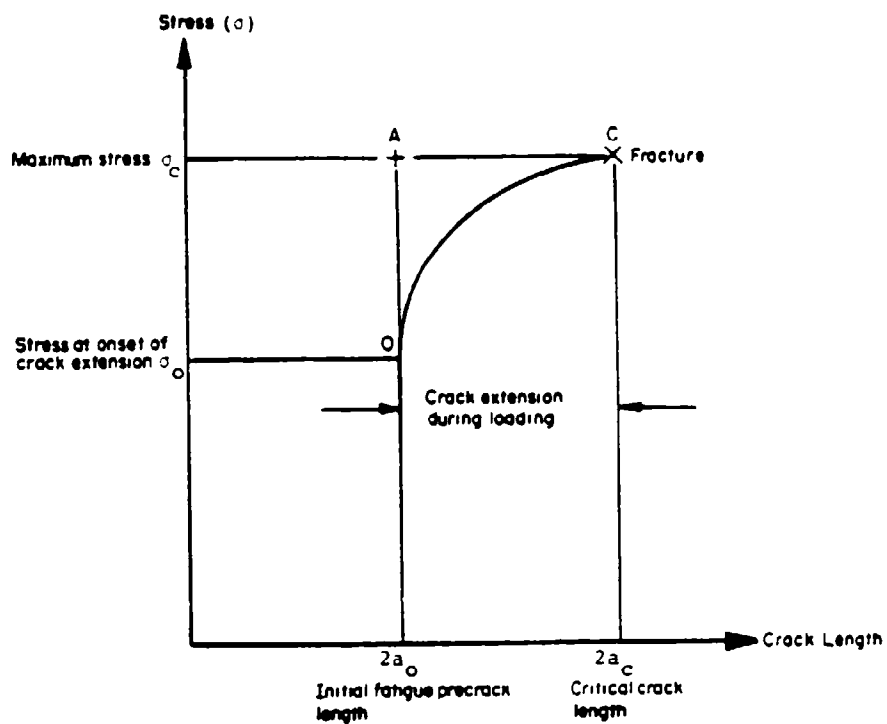


Figure 2.16. Typical Crack Growth Behavior in Plane Stress and Transitional Stress States.

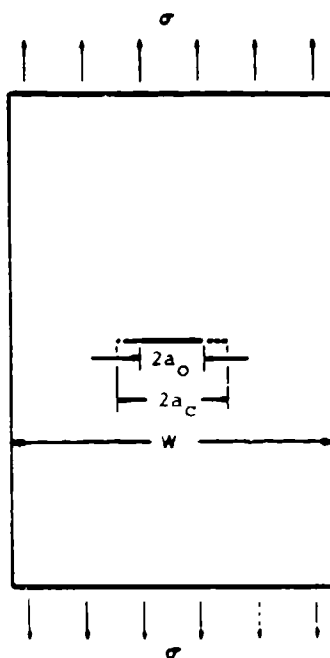


Figure 2.17. Thin-Section, Center-Cracked Tension Panel Configuration.

of available test data is limited to a record of σ_o , $2a_o$, σ_c , and $2a_c$, as indicated in Figure 2.16. It is this information which is compiled and analyzed in this Handbook.

2.2.3 Critical Stress-Intensity Factor (K_c)

There are two clearly identified points that can be noted on the crack growth resistance curve shown in Figure 2.16, i.e. points O and C which are associated with the onset of tearing and critical conditions, respectively. Using a linear elastic fracture mechanics analysis, these two structural conditions can be formulated as

$$K_{\text{ONSET}} = \sigma_o \sqrt{\pi a_o} \left(\text{Sec } \frac{\pi a_o}{W} \right)^{1/2} \quad (2.5)$$

and

$$K_c = \sigma_c \sqrt{\pi a_c} \left(\text{Sec } \frac{\pi a_c}{W} \right)^{1/2} \quad (2.6)$$

using the stress-intensity factor information given in Table 2.3, i.e. Equation SIF.1. As requested by industry engineers, available test information (σ_o , $2a_o$, σ_c , $2a_c$) were reported in the plane stress and transitional fracture toughness tables along with a calculation of the critical fracture toughness level based on Equation 2.6. While stress and crack length information was sometimes available for a calculation of the onset fracture toughness (Equation 2.5), insufficient space in the table precluded reporting this toughness.

Plane stress and transitional fracture behavior absorb much more energy than plane-strain behavior due to the lack of thickness constraint on crack tip plasticity is also insufficient, and the assumption of linear elastic fracture mechanics are violated. The in-plane geometric constraint on crack tip plasticity is required to ensure that gross plasticity is not the controlling mechanisms of fracture. Extensive study

has indicated that the condition for CCP specimen instability for ductile materials is given by a net section stress criteria and not by a fracture (crack) controlled instability criteria. While the fracture toughness values for all plane strain type tests are reported, those values calculated for stress conditions where the net section stress ($\sigma_{net} = \text{Load}/(W-2a_c)$) exceeds 80 percent of the tensile yield strength are marked with an asterisk. Asterisked values are not utilized in any mean or standard deviation calculations summarizing plane-stress fracture critical properties.

2.3 THE APPARENT FRACTURE TOUGHNESS

The apparent fracture toughness (K_{App}) is a plane stress and transitional fracture toughness property that is sometimes utilized as a lower bound on the critical fracture toughness. Its initial purpose was to preclude measurements of the tearing process observed during fracture tests of CCP specimens. As noted in Figures 2.17, and 2.16, the initial crack length ($2a_o$) extends during the loading to the critical crack length ($2a_c$). The two simplest measurements to make in such a fracture test are those of the initial crack length ($2a_o$) and critical (maximum) stress at failure (σ_c). Thus, for simplicity, a K_{App} fracture toughness calculation was made using

$$K_{App} = \sigma_c \sqrt{\pi a_o} \cdot \left(\sec \frac{\pi a_o}{W} \right)^{1/2} \quad (2.7)$$

Equation 2.7 represents the stress-intensity factor corresponding to the stress and crack length condition at point "A" in Figure 2.16. It can be noted by comparing Equations 2.6 and 2.7 that K_{App} will always be less than or equal to K_c since $a_o \leq a_c$. Also, K_{App} will always be greater than or equal to K_{ONSET} since $\sigma_o \leq \sigma_c$. A comparison of the apparent fracture toughness with the onset and critical fracture toughness is shown in Figure 2.18 for a wide center cracked panel (CCP) specimen.

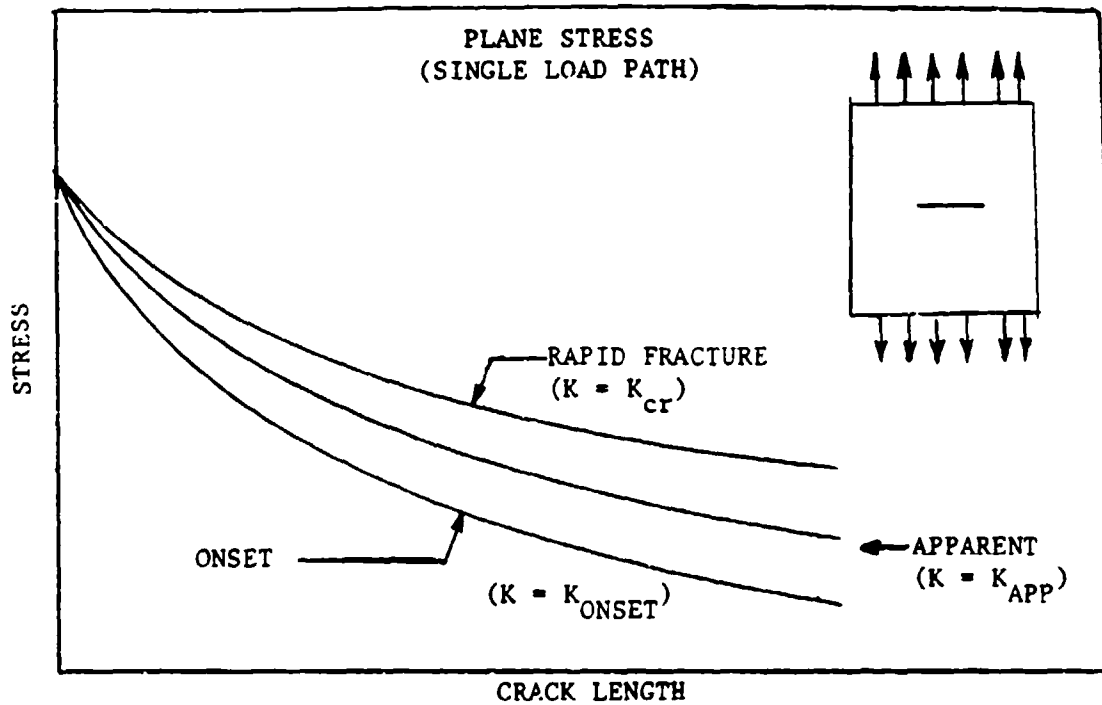


Figure 2.18. Description of the Three Fracture Toughness Criteria that are Utilized to Estimate Residual Strength Under Tearing Fracture Conditions.

When the net section stress ($\sigma_{net} = \text{Load}/(W-2a_0)$) exceeds 80 percent of the tensile yield strength, the K_{App} values are marked with an asterisk. The asterisked values are not utilized in any mean or standard deviation calculations summarizing plane-stress apparent fracture toughness properties.

2.4 R-CURVE (K_R VERSUS Δa_{eff})

The resistance curve (or R-curve) provides a complete description of the tearing fracture behavior illustrated in Figure 2.16. R-curves characterize the resistance to fracture of materials during incremental slow-stable crack extension and result from growth of the plastic zone as the crack extends. ASTM recently formalized the collection and reporting of such curves through a new standard, ASTM Standard E561, covering the standard practice for R-Curve Determination. As stated by ASTM E561: "An R-curve is a continuous record of toughness development in terms of K_R plotted against crack extension in the material as a crack is driven under continuously increased stress-intensity factor, K ."

The value of K_R (toughness) is calculated using standard stress-intensity factor equations evaluated with the instantaneous values of applied stress (σ) and crack length (a), as the crack extends. To account for the effects of plasticity, the measured crack length is enhanced with a plastic zone correction, and an effective crack length (a_{eff}) is actually used in the calculation of K_R . For example, when a CCP specimen is used to collect tearing resistance data, the K_R is calculated based on the standard stress-intensity factor equation (SIF.1) given in Table 2.3.

$$K_R = \sigma \sqrt{\pi a_{eff}} \cdot \left(\text{Sec} \frac{\pi a_{eff}}{W} \right)^{1/2} \quad (2.8)$$

where σ and a_{eff} are the current stress and effective crack length measurements in the test. The effective crack length for optical measurements is calculated from

$$a_{eff} = a + r_y \quad (2.9)$$

where a is the optically measured crack length and

$$r_y = \frac{1}{2\pi} \left(\frac{K}{\sigma_{ys}} \right)^2 \quad (2.10)$$

the plastic zone size for the current applied stress and crack length. If the crack length is automatically monitored by compliance techniques, then the effective crack length is automatically obtained using the two compliance equations presented in ASTM E561.

The K_R value calculated from Equation 2.8 can be described as a function of the increment of physical crack extension ($\Delta a = a - a_0$, a_0 = initial crack length) or as suggested by ASTM 561 as a function of the increment of effective crack length ($\Delta a_{\text{eff}} = (a + r_y) - a_0$). The functions K_R versus Δa and K_R versus Δa_{eff} are referred to as R-curves (or resistance curves). Data presented in this handbook correspond to the use of the ASTM E561 definition of R-curves, i.e. K_R is presented as a function of Δa_{eff} .

One of the fundamental hypotheses behind the application of R-curves to the prediction of tearing type fractures in thin structures and in structures fabricated from ductile materials is that the R-curve (material tearing resistance) is independent of crack length for a given geometry and is independent of geometry and external loading. As long as the structure matches the monotonically increasing stress-intensity factor conditions given by the R-curve, the structure will exhibit the same tearing resistance experienced in the laboratory test specimen. The Damage Tolerant Guidelines Handbook (AFWAL-TR-82-3073) describes how the R-curve can be applied to the calculation of critical stress levels in structures.

2.5 FATIGUE CRACK GROWTH RATE

2.5.1 Fatigue Crack Growth Behavior

Under some loading conditions or environmental conditions, cracks can grow at load levels well below that required to cause fracture. As the crack continues to grow, conditions become more favorable for fracture, and eventually under the applied loading fracture does occur. This process whereby cracks are observed to grow at subcritical load levels is referred to as subcritical crack growth. Illustrated in Figure 2.19 is a fatigue crack growth curve, which shows the type of behavior typically observed during a specific subcritical crack growth process; in this case, damage is done to the material by cyclic (or fatigue) loading. This section addresses properties used to measure fatigue crack growth behavior and Sections 2.6 and 2.7 address properties used to characterize sustained load cracking in an environment.

The objective of fatigue crack growth testing is to determine the rates at which subcritical flaws propagate under cyclic loadings prior to reaching a size critical for fracture. These rates are determined from measurements of the crack extension occurring over an increment of cyclic loading. Typically, these measurements are made by monitoring crack extension optically on the specimen surface during the test. From the basic crack length and cycle count data, the fatigue-crack growth rate is determined as the quotient of the incremental crack growth divided by the incremental cycle count, i.e., $\Delta a / \Delta N$ or da/dN , the slope of the crack growth (life) curve.

The crack growth rate measures the resistance of the material to the applied loading conditions. The similitude parameter that allows data to be transferred from one cracked geometry to another is the range in stress-intensity factor (ΔK). The ΔK parameter is the difference between the maximum and minimum stress-intensity factors (K_{\max} and K_{\min} , respectively) for a cycle of loading. The property of fatigue crack growth rate is described throughout this Handbook as a function of ΔK .

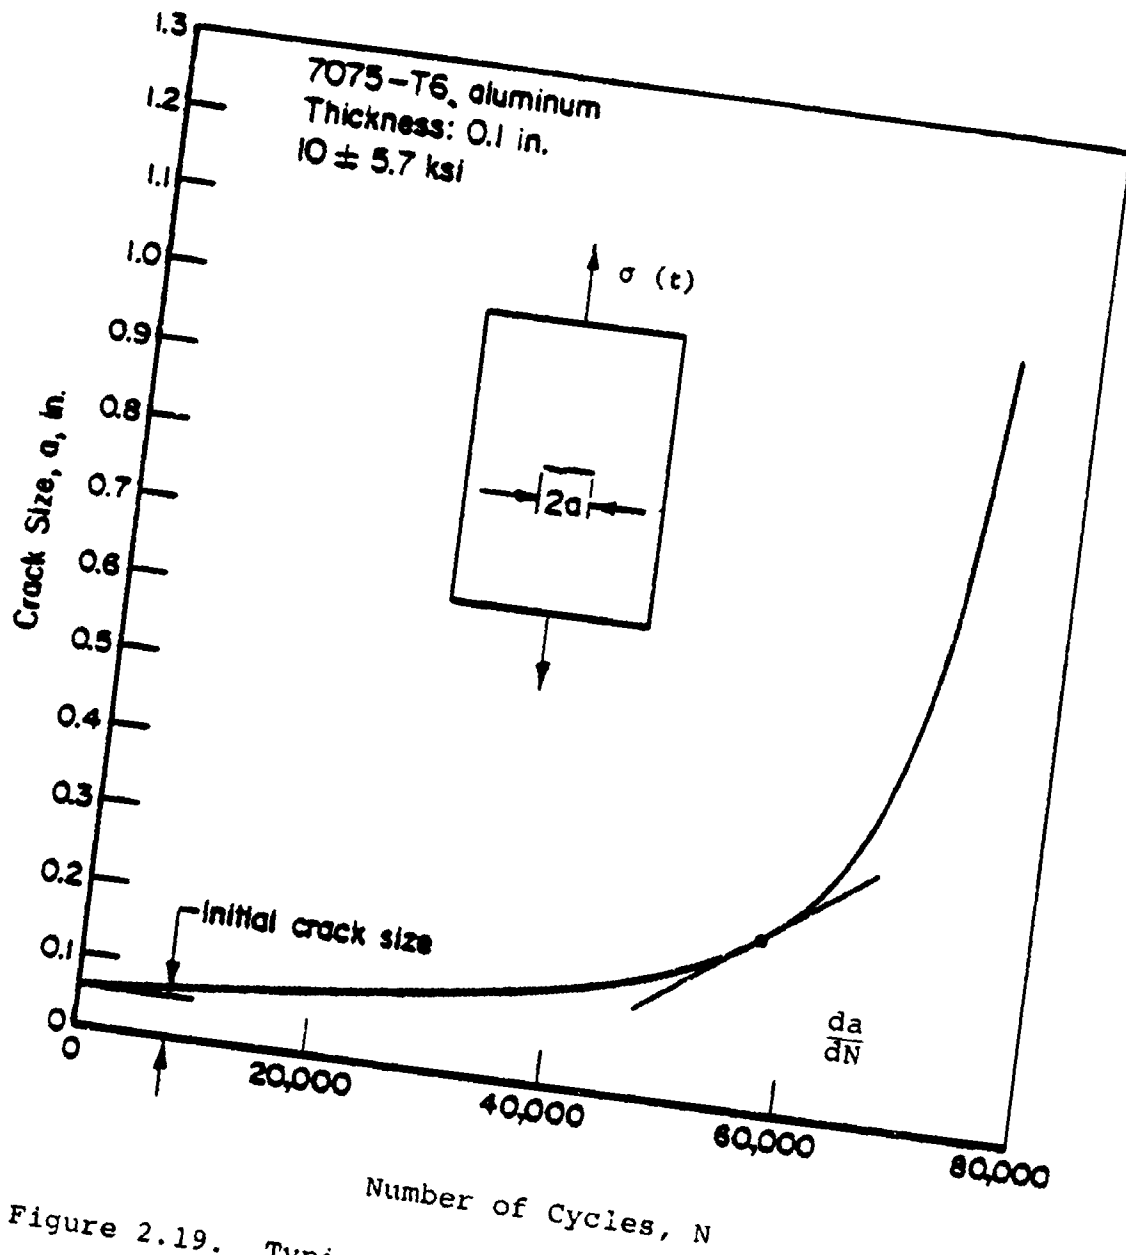


Figure 2.19. Typical Crack Growth-Life Curve.

2.5.2 Data Acceptance Criteria

In general, similar specimen configurations are used for fatigue-crack-growth testing as are used for other types of damage tolerant tests. The applied loads are reduced in magnitude and are cyclic in nature for studies of crack extension under fatigue loading conditions, and the experimental methods are extensions of the fracture testing procedures previously described. Instead of applying either a rising or sustained load to fracture the specimen, a constant amplitude cyclic load is applied to initiate and grow the crack over a significant portion of the specimen width. ASTM recently published a standard testing method, i.e., ASTM E647, which covers the collection and reporting of fatigue crack growth rate data. Most of fatigue crack growth rate data reported in the handbook were collected and reduced utilizing the guidelines and methods described by ASTM E647. For CCP and CT specimen geometries, the ASTM Standard describes 11 explicit criteria for validating the data; these criteria are summarized in Table 2.4. If data were noted to fail only one or two of the recommended criteria and provided a realistic representation of the growth rate behavior, they were incorporated into the handbook. Note is made in the handbook database of da/dN data that failed to meet the ASTM criteria listed in Table 2.4.

2.5.3 Data Reduction Procedures

Data reduction of crack growth rate from the crack length versus cycle count data was by one of two methods. The secant method was chosen when there were seven or less crack length versus cycle count measurements. A five point polynomial movable strip method was used for data with more than seven crack length versus cycle count measurements. This procedure was similar to the seven point method recommended in the ASTM standard; the five point method was chosen to provide additional data points at the extremes of growth rate range.

TABLE 2.4
CRITERIA CHECKS FOR FATIGUE CRACK GROWTH RATE DATA

Criteria No.	ASTM E647 Paragraph	Specimen Type	Criterion
1	7.1.3.1	CT	$\frac{W}{20} \leq B \leq W/4$
	7.1.3.2	CCP	$B \leq W/8$
2	Figure 1	CT	$W \geq 1.00"$
		CCP	None
3	8.6.3	CT and CCP	If $B/W \geq 0.15$ need front and back crack lengths.
4	7.1.1	CT	$a_N \geq 0.2W$
	7.1.2	CCP	None
5	8.3	CT and CCP	$a_1 \geq 0.1B$ or h , whichever is greater
6	8.6.4	CT and CCP	(Front Crack Length-Back Crack Length) < 0.025 W or 0.25 B, whichever is less.
7	8.6.2.1	CT	if $0.25 \leq a/W \leq 0.60$ then $\Delta a \leq 0.02 W$ if $a/W > 0.60$ then $\Delta a \leq 0.01 \bar{W}$
	8.6.2.2	CCP	if $2a/W \leq 0.60$ then $\Delta a \leq 0.03 W$ if $2a/W > 0.60$ then $\Delta a \leq 0.02 W$
8	8.6.2.3	CT and CCP	$\Delta a \geq 0.01"$
9	7.2.1	CT	$W - a \geq \frac{4}{\pi} (K_{\max} / TYS)^2$
	7.2.2	CCP	$P_{\max} / (BW)(1-2a/W) < TYS$
10	8.5.1	CT and CCP	In Test , Load Variation $0 \leq \left \frac{P_{\max a+1} - P_{\max a}}{P_{\max a}} \right \leq 0.10$
11	8.3.1	CT and CCP	(1) In Precracking . $\frac{P_{\max a+1} - P_{\max a}}{P_{\max a}} \leq 0.20$
			(2) $\Delta a \geq (3/\pi) (K_{\max} / TYS)^2$

CT = Compact Tension
CCP = Center Cracked Panel
B = Specimen Thickness
W = Specimen Width
a = Crack Length
 a_N = Notch Size
 a_1 = Fatigue Precrack Length

h = Height of Specimen
 Δa = Change in Crack Length
 P_{\max} = Maximum Load
 K_{\max} = Maximum Stress Intensity
TYS = Tensile Yield Strength
 K'_{\max} = Maximum Stress Intensity at Smaller Crack Length being Considered

It is important to note that the calculation of stress-intensity factor range (ΔK) is the difference between the maximum and minimum stress-intensity factors (K_{\max} and K_{\min} , respectively) as defined in ASTM Standard E647. These calculations are best expressed using equations specific to a given geometry; for illustration purposes, assume that the test specimen geometry is CCP. Then, the maximum and minimum stress-intensity factors are given by

$$K_{\max} = \sigma_{\max} \sqrt{\pi a} \left(\sec \frac{\pi a}{W} \right)^{1/2} \quad (2.11)$$

and

$$K_{\min} = \sigma_{\min} \sqrt{\pi a} \left(\sec \frac{\pi a}{W} \right)^{1/2} \quad (2.12)$$

where σ_{\max} and σ_{\min} are the maximum and minimum stresses in the applied loading cycle. The range of stress-intensity factor is defined as

$$\Delta K = K_{\max} - K_{\min} \quad (2.13)$$

By ASTM convention, if K_{\min} is compressive (negative), then $K_{\min} \equiv 0$, and $\Delta K = K_{\max}$.

2.5.4 Data Reporting Procedures

The presentation of fatigue-crack-propagation rate data is far more complex than the presentation of fracture toughness data (either K_{IC} or K_C) due to the large quantities of data which must be treated. Where a fracture test generally yields a single characteristic toughness value, a fatigue-crack-growth test specimen generally yields from 10 to 100 rate data points, da/dN , which must be evaluated in terms of the stress-intensity factor ΔK range.

The Damage Tolerant Design Data Handbook presents fatigue crack growth rate (da/dn) data in both graphical and tabular formats. A graphical format is used to present da/dN versus ΔK data and the mean trend of these data are tabulated. The

least squares cubic spline approximation method has been selected from those available to provide a practical method for generating tables with fixed ΔK values. A least squares cubic spline approximation is an analytic method of fitting a "French" curve to a data set. The curve is constructed by fitting different cubic polynomials on non-overlapping, connecting subintervals over the range of the independent variable. In the Handbook, the independent variable will be ΔK . The boundary points of the intervals are referred to as knots and the cubic polynomials meet at the knots. The polynomials are also constrained so that the first and second derivatives are continuous at the knots. The result of this process is a smooth curve which passes through the center of the data.

Figure 2.20 is an example of a spline curve fit to a da/dN data set reported by Hudak et al. for 2219-T851 Aluminum alloy. The stress ratio used to establish the data shown was 0.3. The knots are marked in the figure by the large dots.

In general, da/dN data are well enough behaved so that a maximum of five knots was sufficient in generating the handbook tables. The actual number of knots used in fitting a curve to a set of data is a function of the number of da/dN data points and their pattern in $da/dN-\Delta K$ space.

The mean trend table for a set of da/dN data will be generated by selecting points from the spline curve that has been fit to the data. The ΔK values will be chosen such that they are approximately equally spaced in a logarithmic scale and cover the complete range of ΔK values expected. The da/dN values are obtained through the interpolation of the spline curve at the preselected ΔK values. The complete set of ΔK values are: 1.0, 1.3, 1.6, 2.0, 2.5, 3.0, 3.5, 4.0, 5.0, 6.0, 7.0, 8.0, and 9.9 as well as 10 times these values, and 130, 160, and 200.

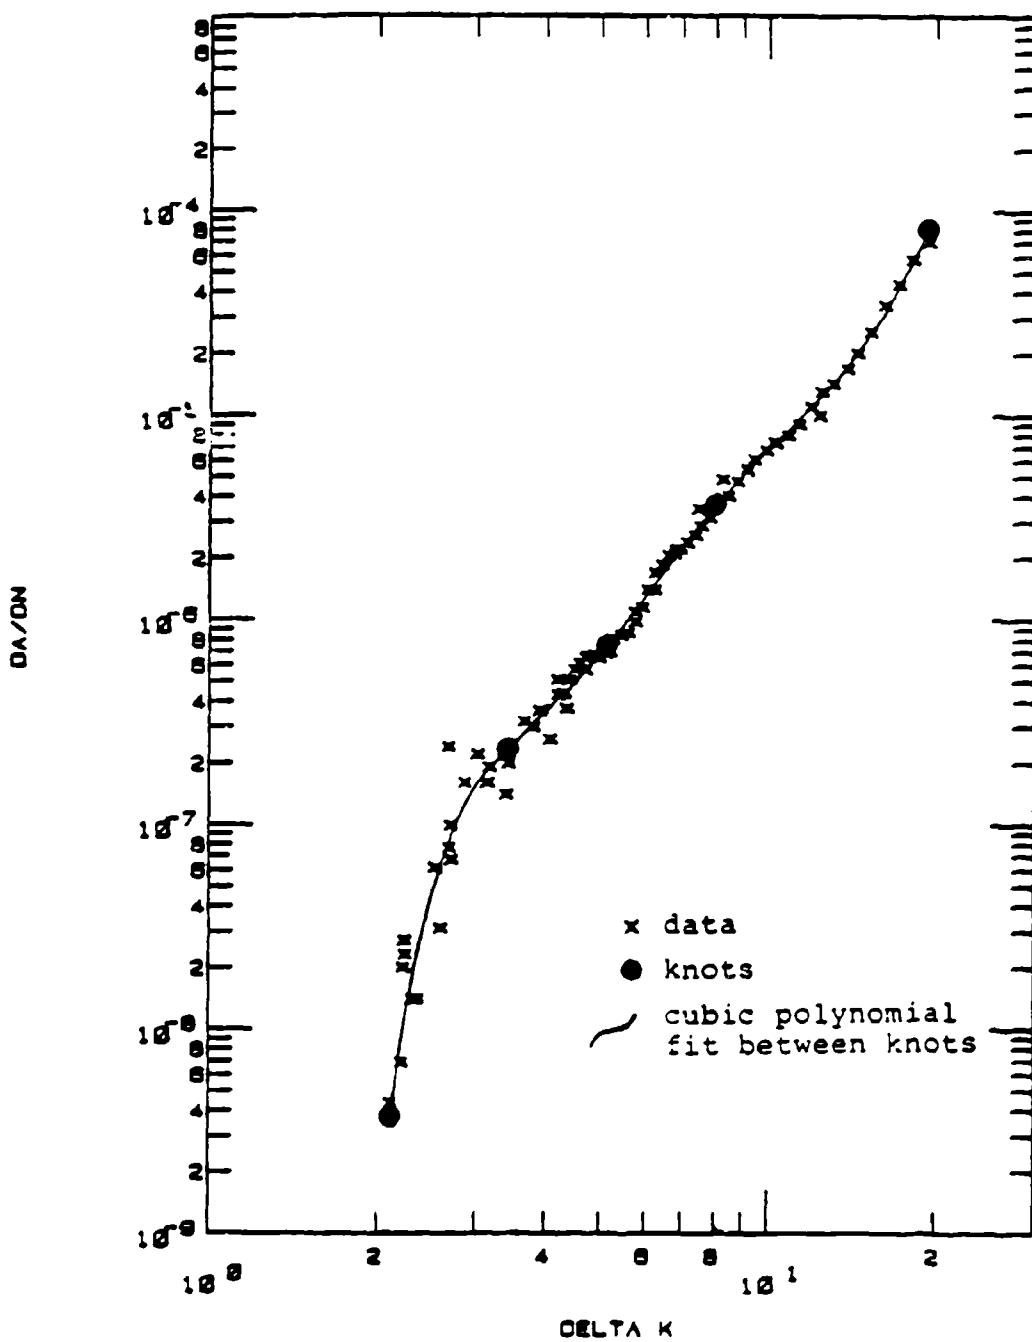


Figure 2.20. A Cubic Spline Curve Fit to FCGR Data for 2219-T851 Aluminum at a Stress Ratio of 0.3.

Because the da/dN data do not always span the complete ΔK range, the table also reports the minimum and maximum da/dN values corresponding to the recorded minimum and maximum ΔK values. The extreme pairs of (ΔK , da/dN) points correspond to the extremes of the spline curve.

Table 2.5 describes the type of table designed for the handbook. The minimum values of ΔK and da/dN as obtained from the spline curves are presented at the top of the table for each data set with a variable such as stress ratio. These tables will be directly opposite the graphical format of the da/dN data. The interpolated da/dN data are listed in the body of the table as a function of the selected ΔK values that span the data sets, and the maximum values of ΔK and da/dN as obtained from the spline curves are presented towards the bottom of the table.

The last two sections of Table 2.5 are utilized to summarize the statistics of the data fitting process. The root mean square percent error (RMSPE) is utilized to describe the statistical accuracy for the spline curve fit at each stress ratio. The RMSPE is given by:

$$\text{RMSPE} = 100 \times \sqrt{\frac{1}{n} \sum_{i=1}^n \left(\frac{y_i - \hat{y}_i}{\hat{y}_i} \right)^2} \quad (2.14)$$

where

y_i = observed da/dN_i at ΔK_i

\hat{y}_i = da/dN interpolated from table at ΔK_i .

The RMSPE is a measure of how close the data lie to the mean trend table and has a similar interpretation to the coefficient of variation, i.e., the smaller the better. The coefficient of variation is used when all the data have the same mean and is calculated by dividing the standard deviation by the mean and multiplying by 100. For da/dN data, the mean da/dN is a function of

TABLE 2.5
 EXAMPLE FATIGUE CRACK GROWTH RATE
 TABLE (2219-T851 Aluminum)

ΔK (Ksi $\sqrt{\text{in}}$)		$da/dN \times 10^4$ inches/cycle					
		R1=-1.0	R2=0.1	R3=0.3	R4=0.5	R5=0.8	
ΔK_{min} at:	R1	1.09	0.00730	0.00336	0.00369	0.00351	0.00112
	R2	7.35					
	R3	2.11					
	R4	1.38					
	R5	1.17					
	1.3	0.0167					0.00429
	1.6	0.0351				0.0176	0.0251
	2.0	0.0676				0.0569	0.0689
	2.5	0.127			0.0451	0.0911	0.128
	3.0	0.216	0.0166	0.152	0.139	0.228	
	3.5	0.336	0.0639	0.246	0.218	0.431	
	4.0	0.488	0.171	0.355	0.339	0.809	
	5.0	0.884	0.566	0.691	0.753	2.60	
	6.0	1.37	1.14	1.30	1.46	7.83	
	7.0	1.91	1.93	2.28	2.50	46.3	
	8.0	2.47	3.09	3.60	3.95		
	9.0	3.08	4.78	5.14	6.07		
	10.0	3.80	7.04	6.86	9.38		
	13.0	7.16	17.0	14.4	38.4		
	16.0	13.2	36.2	30.9			
	20.0	28.3	126.0				
ΔK_{max} at:	R1	20.7	32.0	887.0	81.3	146.0	47.4
	R2	24.7					
	R3	19.3					
	R4	13.8					
	R5	7.01					
root mean square percent error		2.2	80.4	8.6	6.4	6.1	
life prediction ratio summary							
0.0 - 0.5							
0.5 - 0.8			1				
0.8 - 1.25		1	3	1	2	2	
1.25 - 2.0							
> 2.0							

ΔK so this is taken into account when calculating the RMSPE. The RMSPE is an average percent error of the observed da/dN values from the curve established by the mean trend table.

When evaluating the mean trend da/dN description, engineers have come to rely on an evaluation of the ability of the mean trend curve to repredict the initial a versus N data and, in particular, to rely on life prediction ratio (N_p/N_A) which relates the predicted number of cycles (N_p) required to propagate a crack through a specified increment to the actual number of cycles (N_A) observed to propagate a crack through the same increment. Life prediction ratios between 0.8 and 1.25 are considered good and a life prediction ratio of 1.0 is ideal.

As a second measure of how well the mean trend curve fits the data, a summary of the life prediction ratios for the specimens used to generate the mean trend curve is included at the bottom of Table 2.5. This summary defines the number of specimens tested at each stress ratio presented whose life prediction ratios fall within the five intervals: 0.0 to 0.5, 0.5 to 0.8, 0.8 to 1.25, 1.25 to 2.0, and greater than 2.0.

The life prediction ratios summarized at the bottom of Table 2.5 are self predictions and as such will tend to be good. However, the summary is only valid for the data used to generate it and therefore should not be generalized to other situations. The life prediction ratio summary is not intended to predict how well the mean trend curve will predict crack growth for an arbitrary specimen; however, it does illustrate how well the mean trend in FCGR correlates with the lives of the cracks that were used in generating the mean trend.

In order to indicate how well the present method being used does in predicting life ratios, Table 2.6 gives a comparison on sixteen specimens of the Aluminum 2219-T851 at various stress ratios ranging from -1.0 to +0.8. The round-robin LPR resulted from an ASTM study conducted by eight organizations; the average results of the analysis are presented. From Table 2.6, it can be seen that the handbook mean trend method gives results comparable to other methods being used throughout the country.

TABLE 2.6
 FULL INTERVAL COMPARISONS OF
 LIFE PREDICTION RATIOS

<u>NO.</u>	<u>SPECIMEN</u>	<u>STRESS RATIO</u>	<u>ROUND-ROBIN LPR</u>	<u>DTD HB LPR</u>
1.	CT 2219-3	.1	1.03	.9910
2.	CT 4*	.1	0.94	.9095
3.	CT 5	.1	0.91	.8876
4.	CT 6*	.1	0.91	1.0554
5.	CT 11*	.1	1.08	1.0475
6.	CT 20	.1	0.64	.6271
7.	CT 56*	.3	0.99	1.0221
8.	CT 58	.3	0.88	.8400
9.	CT 52	.5	1.07	1.0769
10.	CT 54*	.5	1.00	.9693
11.	CT 60*	.5	1.10	.8354
12.	CT 19	.8	1.71 [†]	***
13.	CT 27*	.8	1.02	.8321
14.	CT 37*	.8	0.92	.9607
15.	CCP 9*	-1.0	0.87	.9856
16.	CCP 11	-1.0	1.14	1.1572
Mean			0.97	0.95
Std. Dev.			0.12	0.13

* Actual Data Were Available for Testing Life Prediction Analysis

*** Stress-Intensity Factor Out of Bounds

[†] Not Included in Calculation of Mean or Std. Dev.

2.6 SUSTAINED-LOAD CRACK GROWTH RATES

2.6.1 Sustained-Load Crack Growth Rate Behavior

Sustained-load crack growth rate behavior is another type of subcritical crack growth behavior exhibited by materials which are sensitive to environmental attack. This type of subcritical crack growth behavior normally exhibits itself as a time-dependent crack growth rate process, whereby cracks are noted to extend under steady-state (sustained) static loading conditions in the presence of environments. Crack growth mechanisms controlling the sustained-load crack growth rate process include: stress-corrosion cracking, hydrogen embrittlement, liquid metal embrittlement, grain boundary separation, and creep. In practice, the time-dependent cracking process has been found to be driven by internal (residual) tensile stresses in the fabricated structure, even in the absence of externally applied loads; typically, however, the stressing condition which drives the crack is provided by external loads.

The objective of sustained-load crack growth testing is to determine the rates at which cracks propagate in pre-cracked specimens subjected to statically applied loads and prescribed environmental conditions. As with fatigue crack growth rate tests, most of the crack length measurements are made optically on the specimen surface during the test. Non-optical methods used to establish cracking include compliance and stress wave analysis techniques. From the basic crack length and time data, the sustained-load crack growth rate is determined as the quotient of the incremental crack growth divided by the incremental time, i.e., $\Delta a/\Delta t$ or da/dt , the slope of the crack growth (time to failure) curve.

The crack growth rate measures the resistance of the material to the applied loading for the specified environment. In this case, the similitude parameter that allows data to be transferred from one cracked geometry to another is the static stress-intensity factor (K_{max}). The K_{max} parameter is the stress-intensity factor evaluated for the applied loading and current crack length. The property of sustained-load crack growth rate (da/dt) is described throughout this Handbook as a function of K_{max} .

2.6.2 Data Acceptance Criteria

For the most part, the testing methodology for da/dt properties follows that utilized to obtain da/dN properties. There are, however, no current ASTM standards that specifically cover the collection of da/dt data. Sustained-load data have been obtained with a variety of specimens including double cantilever beams (DCB), tapered double cantilever beams (TDCB), compact tension (CT) specimens, cantilever beams (CANT), single-edge-notch tensile (SENT) specimens, part-through-surface-crack (PTSC) specimens, and center-cracked panel (CCP) specimens.

One validity criterion that is sometimes applied to da/dt data is that the thickness dimension and crack length must be greater than $2.5 (K_{Ic}/\sigma_{ys})^2$.² No da/dt data were excluded from the 1983 revision, however, based on this criteria due to the scarcity of da/dt data. The reader will find K_{Ic} , σ_{ys} and thickness reported with da/dt data whenever these were available.

Readers should note that sustained load crack growth rate data in aluminum alloys in planes other than those parallel to the surface of rolled plates are questionable because of the localized corrosion that occurs on the planes even though the initial notch and crack orientation are normal to these planes.

2.6.3 Data Reduction Procedures

Data reduction of sustained-load crack growth rates was accomplished using the secant method applied to crack length (a) measurements recorded as a function of time (t). These calculations and those of static stress-intensity factor were provided to the data processing organization for reformatting.

2.6.4 Data Reporting Procedures

The data reporting procedures for sustained-load cracking data are similar to those discussed in subsection 2.5.4 for fatigue crack growth rates. The major difference between the two subcritical cracking rate reporting procedures is that da/dt vs K_{max} describes the sustained-load behavior whereas da/dN vs ΔK describes the fatigue behavior. The reader might also note that no a vs t were available to compare with the integrated crack growth mean trend data and therefore no life prediction ratios were presented.

2.7 THRESHOLD STRESS INTENSITY (K_{ISCC})

2.7.1 The Threshold

In many environments, materials exhibit a condition whereby cracks are not observed to grow if the static stress intensity factor is below a critical level, designated K_{ISCC} . This property is specific for a given material in a given environment within a specified time period. In high-strength materials, K_{ISCC} may be only a small fraction of the plane-strain fracture-toughness value (K_{IC}) of the material. In lower strength tougher materials where plane-strain conditions still prevail, K_{ISCC} may approach or equal K_{IC} , if the environment has little or no effect on the stress intensity required to propagate a crack.

K_{ISCC} data have been obtained with a variety of specimens including: Cantilever beam (CANT), 3-point loaded bend beam (ND), 4-point loaded bend beam (4-NB), Single-edge-notch tensile (SENT), Center-cracked tensile (CNT), Part-

through surface-crack (PTSC), Compact tension (CT), Bolt-loaded WOL (BWOL), Double cantilever beam (DCB), and Tapered or contoured double cantilever beam (TDCB). All specimens are notched and precracked by fatigue, and many specimens are side grooved (SG) to ensure that the crack propagates in one plane perpendicular to the applied tensile loading and also to minimize the contribution of shear lips at the edges of the crack.

The types of specimens for determining K_{Isc} fall into two broad categories: those that are loaded by weights or tensile machines (see Figure 2.21) and those that are self-loaded as by bolts. The former require bulky setups to accommodate lever arms, weights, and tensile machines while the latter are compact and portable. Thus the environment is applied to the externally loaded specimens usually in the form of a small container sealed onto the specimen, while the self-loaded specimen may be completely immersed in the environment.

Under dead-weight loading conditions, the usual practice is to run a number of specimens at various stress intensities less than K_{Ic} for a finite length of time (more than 24 hours and usually about 500 hours) to establish K_{Isc} . Another method is to step load a single specimen until the crack starts to propagate. This method requires holding after each load increment for a sufficient time to establish that crack propagation does not occur.

Under bolt self-loading conditions, sufficient load is first applied to the bolt to cause the crack to extend beyond its precracked position. The specimen is then exposed to the environment. As the crack propagates in the environment, the stress-intensity factor decreases at the tip of the advancing crack until the crack arrests at K_{Isc} . Specimen length must be sufficient to ensure that the crack arrests before completely penetrating the specimen, thus assuring that a value is obtained for K_{Isc} .

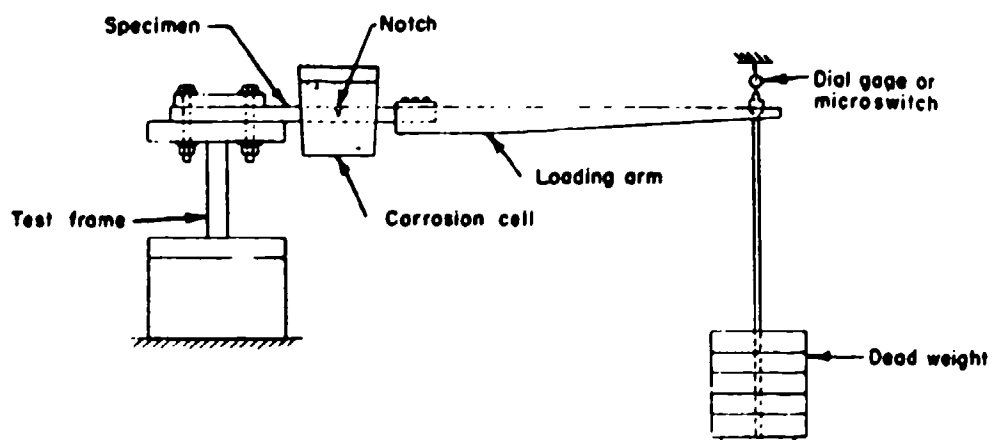


Figure 2.21. Schematic Drawing of Fatigue Cracked Cantilever Beam Test Specimen and Fixtures.

2.7.2 Conditions for Validity of Data

There are no ASTM standards that specifically cover the collection of K_{ISCC} data. The criterion typically used to validate K_{ISCC} data is that the thickness dimension (B) and crack length (a) are greater than the ASTM E399 requirement for plane-strain fracture toughness, i.e., that B and $a \geq 2.5 (K_{IC}/\sigma_{ys})^2$. Data which did not meet this criterion are identified in the K_{ISCC} tables with an asterisk. Many tests reveal a drastic reduction in the stress intensity required to propagate a crack even though the $2.5 (K_{IC}/\sigma_{ys})^2$ criterion is not met. Although these data are not recommended for material selection and design purposes, they do indicate a qualitative effect.

CHAPTER 3
STAINLESS STEEL ALLOY SECTION

3.0	Stainless Steel Material Summaries
3.1	AFC 260
3.2	AFC 77
3.3	AFC 77 (VAR)
3.4	AM 355
3.5	AM 362
3.6	AM 364
3.7	Custom 455
3.8	PH 13-8Mo
3.9	PH 14-8 Mo
3.10	PH 15-7 Mo
3.11	15-5PH
3.12	15-5 PH(AM)
3.13	15-5 PH (VM)
3.14	17-4 PH
3.15	17-7 PH
3.16	304
3.17	316
3.18	347
3.19	Bibliography

Table 3.0.1

AVAILABLE DATA FOR STAINLESS STEEL ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	K1C	K2C	R	CURVES	DA/DM	DA/DT	R18CC
AFC 260	2200F 1HR 1900F 1HR 08 -100F 1HR -320F 1HR 800F 2+2 HR	PLATE							X
	2200F 1HR 1900F 1HR 08 -100F 1HR -320F 1HR 1090F 2+2HR	PLATE							X
	2200F 1HR 1900F 1HR 08 -100F 1HR -320F 1HR 900F 2+2 HR	PLATE							X
	2200F 1HR 1900F 1HR 08 -100F 1HR -320F 1HR 1000F 2+2 HR	PLATE							X
	AUSTENIZED AT 2010F, QUENCHED TEMPERED AT 810F	SHEET						X	
	1800F 1HR 08, -100F 0.5HR, 500F 2+2 HR (COARSE GRAIN)	PLATE							X
	1800F 1HR 08, -100F 0.5HR, 1000F 2+2 HR (COARSE GRAIN)	PLATE	X						X
	1800F 1HR 08, -100F 0.5HR, 500F 2+2 HR (FINE GRAIN)	PLATE							X
AFC 77	1800F 1HR 08, -100F 0.5HR, 1000F 2+2 HR (FINE GRAIN)	PLATE	X						X
	1800F 1HR, 08, -100F 0.5HR, 700F 2+2HR (COARSE GRAIN)	PLATE	X						X
	1800F 1HR, 08, -100F 0.5HR, ROOF 2+2HR (COARSE GRAIN)	PLATE	X						X
	1800F 1HR, 08, -100F 0.5HR, 700F 2+2HR (FINE GRAIN)	PLATE	X						X
	1800F 1HR, 08, -100F 0.5HR, ROOF 2+2HR (FINE GRAIN)	PLATE	X						X
	1800F 1HR, 08, -100F 0.5HR, ROOF 2+2HR (FINE GRAIN)	PLATE	X						X
	1800F 1HR, 08, -100F 0.5HR, ROOF 2+2HR (FINE GRAIN)	PLATE	X						X
	1800F 1HR, 08, -100F 0.5HR, ROOF 2+2HR (FINE GRAIN)	PLATE	X						X

Table 3.0.1 (Con't)

AVAILABLE DATA FOR STAINLESS STEEL ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	KIC	KC	R	CURVES	DA/DN	DA/DT	KIBCC	
AFC 77	1800F 1HR. OG. -100F 1HR. 700F 2+2HR	ROUND BAR	X							
	1800F 1HR. OG. -100F 1HR. 800F 2+2HR	ROUND BAR	X							
	1900F 1HR. OG. -100F 1HR. 800F 2+2HR	ROUND BAR	X							
	2000F 1HR OG. -100F 0.5HR 1400F 2+2 HR	BAR							X	
	2000F 1HR OG. -100F 0.5HR 500F 2+2HR	BAR							X	
	2000F 1HR OG. -100F 0.5HR 700F 2+2 HR	BAR							X	
	2000F 1HR OG. -100F 0.5HR 800F 2+2 HR	BAR							X	
	2000F 1HR OG. -100F 0.5HR 900F 2+2 HR	BAR							X	
	2000F 1HR OG. -100F 0.5HR 1100F 2+2 HR	BAR							X	
	2000F 1HR OG. -100F 0.5HR 500F 2+2HR + 10 PCT CM, 1000F	BAR							X	
	2000F 1HR OG. -100F 0.5HR 500F 2+2HR + 10 PCT CM, 700F	BAR							X	
	2000F 1HR OG. -100F 0.5HR 500F 2+2HR + 20 PCT CM, 700F	BAR							X	
	2000F 1HR. OG. -100F 1HR. 900F 2+2HR	ROUND BAR	X							
	2000F 1HR. OG. -100F 1HR. 800F 2+2HR	ROUND BAR	X							
	2100F 1HR. FC TO 1700F HR.D 1HR. OG. -100F 4HR. 500F 2+2 HR	FORGING								X

Table 3.0.1 (Con't)

AVAILABLE DATA FOR STAINLESS STEEL ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	KIC	KC	R	CURVES	DA/DN	DA/DT	KISCC
AFC 77 (VAR)	1700F 1HR.00 2100F 1HR. MOVED TO FCE AT 1933F. WELD 1HR.00. -100F 24HR. 900F. 2+2HR	FORGING	X						
	2100F 1HR. MOVED TO FCE AT 1900F. WELD 1HR.00. -100F 4HR. 300F 2+2HR	FORGING	X						
AM 355	MOD SCT1000	BAR							X
	SCT 850	PLATE BAR							X X
AM 362	SCT1000	PLATE BAR							X X
	H 900	BAR							X
AM 364	H1000	BAR							X
	H 850	FORGING							X
CUSTOM 453	H 950	FORGING							X
	H 900	FORGING							X
	H 950	FORGING							X
	H1000	FORGING						X	
	1500F 1HR.00. 950F 4HR. AC	FORGING	X						
	1500F 1HR.00. 900F 4HR. AC	FORGING	X						

Table 3.0.1 (Con't)
AVAILABLE DATA FOR STAINLESS STEEL ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	KIC	MC	R	CURVES	DA/DN	DA/DT	KISCC	
PH113-880	ANNEALED	EXTRUDED BAR						X		
		FORGING	X							
		FORGED BAR	X							
	AUSTENITE COND AND TRANSFORMED AT 38F. AGED 1015F	SHEET	X							X
		FORGING	X							X
		ROLLED BAR	X							X
	H 950	FORGED BAR	X							X
		BAR								X
		EXTRUDED BAR								X
	H1000	SHEET	X							
		PLATE	X							
		FORGING	X					X		
		EXTRUSION	X					X		X
		FORGED BAR	X					X		X
		ROLLED BAR	X					X		X
H1025	BAR									
	BILLET						X			
	EXTRUDED BAR						X			
H1050	SHEET	X								
	ROLLED BAR	X							X	
MILL 1700F. LAB 1050F 4HR	FORGING	X								
	FORGING	X								
	FORGING	X								
MILL 1700F. LAB 1600F. 1000F 4HR	ROLLED BAR	X							X	
	ROUND BAR									
MILL 1700F. LAB 1500F. 1000F 4HR	ROLLED BAR	X							X	
	ROUND BAR									
R11 950	ROLLED BAR	X							X	
	ROUND BAR									
R11 975	ROLLED BAR	X							X	
	ROUND BAR									

Table 3.0.1 (Con't)

AVAILABLE DATA FOR STAINLESS STEEL ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	K1C	KC	R	CURVES	DA/DN	DA/DT	KISCC
PH13-8PH	RH1010	ROLLED BAR ROUND BAR	X						X
	TYS=140KSI	PLATE							X
	TYS=160KSI	PLATE							X
	TYS=190KSI	PLATE							X
	TYS=200KSI	PLATE							X
	TYS=210KSI	PLATE							X
PH14-8PH	SRH1050	SHEET		X					
	RH 930	ROLLED BAR BAR	X						X
PH15-7PH	RH1050	ROLLED BAR	X						X
	TH1050	BAR							X
15-3PH	H 900	ROLLED BAR BAR	X						X
	H1025	BAR					X		
	H1150H	BAR							X
	TYS=150-165KSI	BILLET						X	
	TYS=150-165KSI	FORGING	X						
15-5PH(2M)	H 910	FORGING							X
	H1000	FORGING							X

Table 3.0.1 (Con't)

AVAILABLE DATA FOR STAINLESS STEEL ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	K1C	KIC	R	CURVES	DA/DM	DA/DT	K1BCC
15-5PH(VM)	H 700	FORGING							X
	H1090	FORGING							X
17-4PH	H 900	PLATE BAR				X			X
	H 975	ROLLED BAR	X						
	H1000	BAR							X
	H1025	ROUND BAR CASTING	X			X	X		
17-7PH	H11 950	BAR							X
	H11050	ROLLED BAR BAR	X						X
	H11050	PLATE BAR				X			X
304	ANNEALED	SHEET PLATE				X	X		
	ANNEALED & AGED	PLATE				X			
316	ANNEALED	PLATE				X			
	ANNEALED AT 1950F, 1HR. W0	PLATE				X			
317	W0 IN. FROM CENTERLINE	WELDMENT				X			
	AT CENTERLINE	WELDMENT				X			
	AT HEAT AFFECTED ZONE	WELDMENT				X			

Table 3.0.2

PLANE STRAIN FRACTURE TOUGHNESS VALUES OF STAINLESS STEEL ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ HT	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	K _{IC}		K _{ISCC}			
				L-T	T-L	L-T	T-L		
				SPECIMEN MEAN THICK °	STD. DEV.	SPECIMEN MEAN THICK °	STD. DEV.		
AFC 77 (VAR)	1700F 1HR.00	FORGING	6.00	0.50	48.6	3.1	0.50	50.6	1.3
	2100F 1HR. MOVED TO FCC AT 1900F. HELD 1HR.00. -100F 2HR.00. 900F. 2+2HR								
CUSTOM 455	2100F 1HR.	FORGING	6.00	2.01	110.5	4.9	2.01	108.0	5.7
	MOVED TO FCC AT 1900F. HELD 1HR.00. -100F 4HR.00. 900F 2+2HR								
CUSTOM 455	1500F 1HR.00.	FORGING	4.00	0.48	72.1	7.8	---	---	---
	950F 4HR. AC								
PH13-8MO	1500F 1HR.00.	FORGING	4.00	0.48	46.2	3.3	---	---	---
	900F 4HR. AC								
PH13-8MO	ANNEALED	FORGING	3.00	1.01	114.1	15.7	1.00	99.6	22.4
	AUSTENITE COND AND TRANSFORMED AT 36F. ARED 1015F								
PH13-8MO	H 950	SHEET	1.00-2.25	1.00	58.4	6.5	1.00	69.4	16.1

PH13-8MO	---	FORGING	4.00-8.00	1.00	70.3	16.0	---	---	---

PH13-8MO	---	ROLLED BAR	2.25	1.00	66.9	2.9	1.00	63.5	1.7

PH13-8MO	---	SHEET	1.50-2.25	1.00	105.6	4.8	1.00	96.2	5.2

PH13-8MO	---	PLATE	4.00	0.98	94.7	3.6	---	---	---

PH13-8MO	---	FORGING	2.75-8.00	0.75	101.6	11.0	0.75	88.1	17.1

PH13-8MO	---	EXTRUSION	1.50	1.00	68.5	5.5	1.00	66.2	2.1

• MINIMUM SPECIMEN THICKNESS (IN)

Table 3.0.2 (Con't)

FLANE STRAIN FRACTURE TOUGHNESS VALUES OF STAINLESS STEEL ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ HT	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	K1C (KSI BORT(IN))		L-T		T-L		B-L	
				SPECIMEN THICK *	MEAN	STD. DEV.	SPECIMEN THICK *	MEAN	STD. DEV.	SPECIMEN THICK *	MEAN
PH13-8MO	H1000	FORGED BAR	1.00	1.00	114.2	0.9	1.00	122.7	3.0	---	---
			1.50	1.00	90.0	7.1	1.00	75.0	4.2	---	---
			2.25	1.00	103.1	4.6	1.00	94.8	7.8	0.75	92.2
PH15-7MO	RH 950	ROLLED BAR	1.25	---	---	---	1.00	30.6	0.1	---	---
		ROLLED BAR	1.25	---	---	---	1.00	40.2	1.5	---	---
15-5PH	H 900	ROLLED BAR	2.25	---	---	---	1.00	72.7	4.5	---	---
		FORGING	---	---	---	---	1.50	94.8	6.9	---	---
17-7PH	RH1050	ROLLED BAR	1.25	---	---	---	1.00	47.0	0.7	---	---

* MINIMUM SPECIMEN THICKNESS (IN).

Table 3.0.3.1

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE
STRESS INTENSITY FACTOR FOR STAINLESS STEEL ALLOYS

TEST CONDITIONS:

SPECIMEN
ORIENTATION Unknown

ENVIRONMENT: LAB AIR AT R. T.

STRESS RATIO: 0.05-0.10

FREQUENCY: 3.00-30.00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN)) =					
					2.5	3.0	10.0	20.0	50.0	100.0
304	ANNEALED	SHEET	0.05	10.00		.163		3.07		
	ANNEALED	SHEET	0.05	15.00		.133		2.83		
	ANNEALED	SHEET	0.10	1.67				2.86		
	ANNEALED	SHEET	0.10	6.00				2.56		
	ANNEALED & AGE	PLATE	0.05	3.00				1.38		
316	ANNEALED AT 1950F. 1HR. WQ	PLATE	0.05	10.00				2.39		
347	.050 IN FROM CENTERLINE	WELDMENT	0.10	30.00						9.83
	AT CENTERLINE	WELDMENT	0.10	30.00						13.1
	AT HEAT AFFECTED ZONE	WELDMENT	0.10	30.00						17.5

Table 3.0.3.2

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR STAINLESS STEEL ALLOYS

TEST CONDITIONS:

SPECIMEN ORIENTATION L-T ENVIRONMENT: LAB AIR AT R. T.
 STRESS RATIO 0.00-0.10 FREQUENCY: 0.03-30.00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN)) =					
					2.5	3.0	10.0	20.0	50.0	100.0
CUSTOM 455	H1000	FORGING	0.10	10.00-30.00				2.78		
PH13-8MO	H1000	FORGING	0.10	1.00-10.00			9.44	31.9	127.	
	H1000	BAR	0.02	1.00				31.6		
17-4PH	H 900	PLATE	0.08	20.00			303	3.38	53.1	
17-7PH	TH1030	PLATE	0.10	20.00			0232	433		
304	ANNEALED	PLATE	0.00	.03					56.0	
	ANNEALED	PLATE	0.00	6.67				1.92	28.5	

Table 3.0.3.3

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE
STRESS INTENSITY FACTOR FOR STAINLESS STEEL ALLOYSTEST CONDITIONS:

SPECIMEN ORIENTATION T-L ENVIRONMENT: LAB AIR AT R.T.
STRESS RATIO 0.00-0.10 FREQUENCY: 1.00-30.00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS (MSI SQRT(IN)) =
					2.5 5.0 10.0 20.0 50.0 100.0
CUSTOM 435	H1000	FORGING	0.10	10.00	25.0
	H1000	FORGING	0.10	20.00	3.00
	H1000	FORGING	0.10	20.00-30.00	2.58
PH13-8ND	H1000	FORGING	0.10	1.00-10.00	5.37 32.1 143
15-5PH	H1025	BAR	0.05	10.00	15.3 155
17-4PH	H1025	ROUND BAR	0.10	30.00	.0607 2.00
17-7PH	T1050	PLATE	0.10	20.00	.0265 .388 4.44
304	ANNEALED	PLATE	0.00	6.60	1.86 32.5

TABLE 3.0.4
 INDIVIDUAL STRESS CORROSION CRACKING THRESHOLD DATA FOR
 STAINLESS STEEL ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ FIT	PRODUCT FORM	SPECIMEN ORIENTATION	ENVIRONMENTS			K_{ISCC} (ksi/in)	
				SUMP TANK WATER	3.5% NaCl	20% NaCl		
				SEACOAST	ATMOSPHERE	INDUST.	ATMOSPHERE	
AFC 77	1800F 1HR OQ, -100F 0.5 HR, 500F 2&2 HR, (Coarse G.S.)	P	---	15				
	2000F 1HR OQ, -100F 0.5 HR, 700F 2&2 HR	B	---	50				
	2000F 1HR OQ, -100F 0.5 HR, 800F 2&2 HR	B	---	40				
	2000F 1HR OQ, -100F 0.5 HR, 900F 2&2 HR	B	---	15				
	2000F 1HR OQ, -100F 0.5 HR, 1100F 2&2 HR	B	---	10				
	2000F 1HR OQ, -100F 0.5 HR, 500F 2&2 HR, & 10PCT CM, 1000F	B	---	30				
	2000F 1HR OQ, -100F 0.5 HR, 500 2&2 HR, & 10PCT CM, 700F	P	---	90				
	2000F 1HR OQ, -100F 0.5 HR, 500F 2&2 HR, & 20 PCT CM, 700F	B	---	48				
	2200F 1HR, 1900F 1HR OQ, -100F 1HR, -100F 1HR, 900F, 2&2 HR	P	T-L	40				
	2200F 1HR, 1900F 1HR OQ, -100F 1HR, -100F 1HR 1000F 2&2 HR	P	T-L	45				
	2200F 1HR, 1900F 1HR OQ, -100F 1HR, -100F 1HR, 1050F 2&2 HR	P	T-L	37				
	AN 355	SCT 850	P	T-L	8	24	45	
			B	T-L	6	18	18	
	SCT 1000		P	T-L	37	52	99	
		B	T-L	28	35	66		

Table 3.0.4 (Continued)

ALLOY	CONDITION/ HT	PRODUCT FORM	SPECIMEN ORIENTATION	K _{ISCC} (Kai/in)				
				SUMP TANK WATER	3.5% NaCl	ENVIRONMENTS 20% NaCl	SEACOAST ATMOSPHERE	INDUST. ATMOSPHERE
AM 362	H900	B	---		12			
	H1000	B	---		31			
CUSTOM 455	H900	P	---		60			
	H950	F	---		72			
PH13-8MO	H950	F	T-L		74			
		FB	L-T	48		46	31	59
		B	T-L					
H1000	H1000	E	L-T	55				
		FB	L-T	88				
		FB	T-L	100				
		FB	L-T	70				
		B	T-L			65	44	83
H1050	H1050	F	T-L		120			
		B	---		14			
PH15-7MO	H1050	B	---		18			
		B	---					
15-5 PH	H900	B	---			33	36	68
		P	---		56			
17-4 PH	H900	B	---		52			
17-7 PH	H1050	B	T-L			65	12	24
		B	---		16			

Table 3.1.3.1

CONDITION	--PRODUCT--		TEST SPEC	YIELD	STR	ENVIRONMENT	SPECIMEN		K (IBCC)	STAN	TEST	DATE		
	FORM	THICK					WIDTH	THICK					LENGTH	CRACK
	(IN)	(F)	(RBT)	(R.T.)	(PCT)	(IN)	(IN)	(IN)	(IN)	(IN)	(MIN)			
2200F 1HR 1900F 1HR -320F 1HR	P	0.36	R.T.	T-L	3.5	PCT	MACL	1.500	0.480	CANT*	64.00	59.00*	1971	80685
	OG	-100F	1HR											
2200F 1HR 1900F 1HR -320F 1HR	P	0.36	R.T.	T-L	185	0.35	PCT	MACL	1.500	0.480	CANT*	37.00	1971	80685
	OG	-100F	1HR											
2200F 1HR 1900F 1HR -320F 1HR	P	0.36	R.T.	T-L	196	0.35	PCT	MACL	1.500	0.480	CANT*	47.00	1971	80685
	OG	-100F	1HR											
2200F 1HR 1900F 1HR -320F 1HR	P	0.36	R.T.	T-L	206	0.35	PCT	MACL	1.500	0.480	CANT*	45.00	1971	80685
	OG	-100F	1HR											

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5 (KIBCC/TYB) SQUARED

Table 3.2.2.1

CONDITION	--PRODUCT--		YIELD STRENGTH (KSI)	SPECIMEN		CRACK LENGTH (IN)	2.9* CRACK LENGTH (K(1C)/TYS)**2 (IN)	K(1C) MEAN (K(1C))	STANDEV (K(1C))	DATE	REFER
	FORM	THICK (IN)		WIDTH (IN)	THICK (IN)						
1800F 1HR. 0G. P -100F 0.5HR. 1000F 2+2HR	P	0.36	173.0	1.500	0.500	MB	----	0.05	23.00	1969	74720 (1)
1800F 1HR. 0G. P -100F 0.5HR. 700F 2+2HR	P	0.36	163.0	1.500	0.500	MB	----	0.11	38.00	1969	74720 (1)
1800F 1HR. 0G. P -100F 0.5HR. 800F 2+2HR	P	0.36	208.0	1.500	0.500	MB	----	0.05	28.00	1969	74720 (1)
1800F 1HR. 0G. P -100F 0.5HR. 700F 2+2HR	P	0.36	203.0	1.500	0.500	MB	----	0.15	49.00	1969	74720 (1)
1800F 1HR. 0G. P -100F 0.5HR. 800F 2+2HR	P	0.36	224.0	1.500	0.500	MB	----	0.05	31.00	1969	74720 (1)
1800F 1HR. 0G. P -100F 0.5HR. 1000F 2+2HR	P	0.36	232.0	1.500	0.500	MB	----	0.04	30.00	1969	74720 (1)
1800F 1HR. 0G. BR -100F 1HR. 700F 2+2HR	BR	3.00	185.0	1.500	0.480	MB	----	0.14	44.00	1968	64302 (1)
1800F 1HR. 0G. BR -100F 1HR. 800F 2+2HR	BR	3.00	213.0	1.500	0.480	MB	----	0.05	29.00	1968	64302 (1)
1900F 1HR. 0G. BR -100F 1HR. 800F 2+2HR	BR	3.00	222.0	1.500	0.480	MB	----	0.28	74.00	1968	64302 (1)
2000F 1HR. 0G. BR -100F 1HR. 900F 2+2HR	BR	3.00	207.0	1.500	0.480	MB	----	0.29	70.00	1969	76136 (1)
2000F 1HR. 0G. BR -100F 1HR. 900F 2+2HR	BR	3.00	214.0	1.500	0.480	MB	----	0.17	56.00	1969	76136 (1)

NOTES:
(1) COMPOSITION (WT PERCENT) 16C.0 18FM.0 013P.0 021S.0 13S1.0 21NI.14. 0CR.5 02MO.13 4CO.0 23V.0 04N
THESE DATA ARE AVERAGE VALUES

Table 3.2.3.1

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.2.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL AFC 77

CONDITION: AUSTENITIZED AT 2010F, QUENCHED & TEMPERED AT 810F

K MAX (KSI*IN**1/2)	DA/DT (10**-3 IN/HOUR)			
	A	B	C	D
	E=			
	DISTILLED WATER			
A: 20.00	1.01			
B: 25.00	4.55			
C: 30.00	2.67			
D: 35.00	3.21			
	17.5			
A: 47.00	5213.			
B: 47.00				
C: 47.00				
D: 47.00				

ROOT MEAN SQUARE 62.42
PERCENT ERROR

CONDITION/HT: AUSTENITIZED AT 2010F, QUENCHED & TEMPERED AT 810F
 FORM: 0.08" TH SHEET
 SPECIMEN TYPE:
 ORIENTATION:
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK:
 SPECIMEN WIDTH:
 CRACK LENGTH (A₀):
 K_{ISCC}:
 REFERENCES: 85544

STAIN.
STEEL

AFC 77

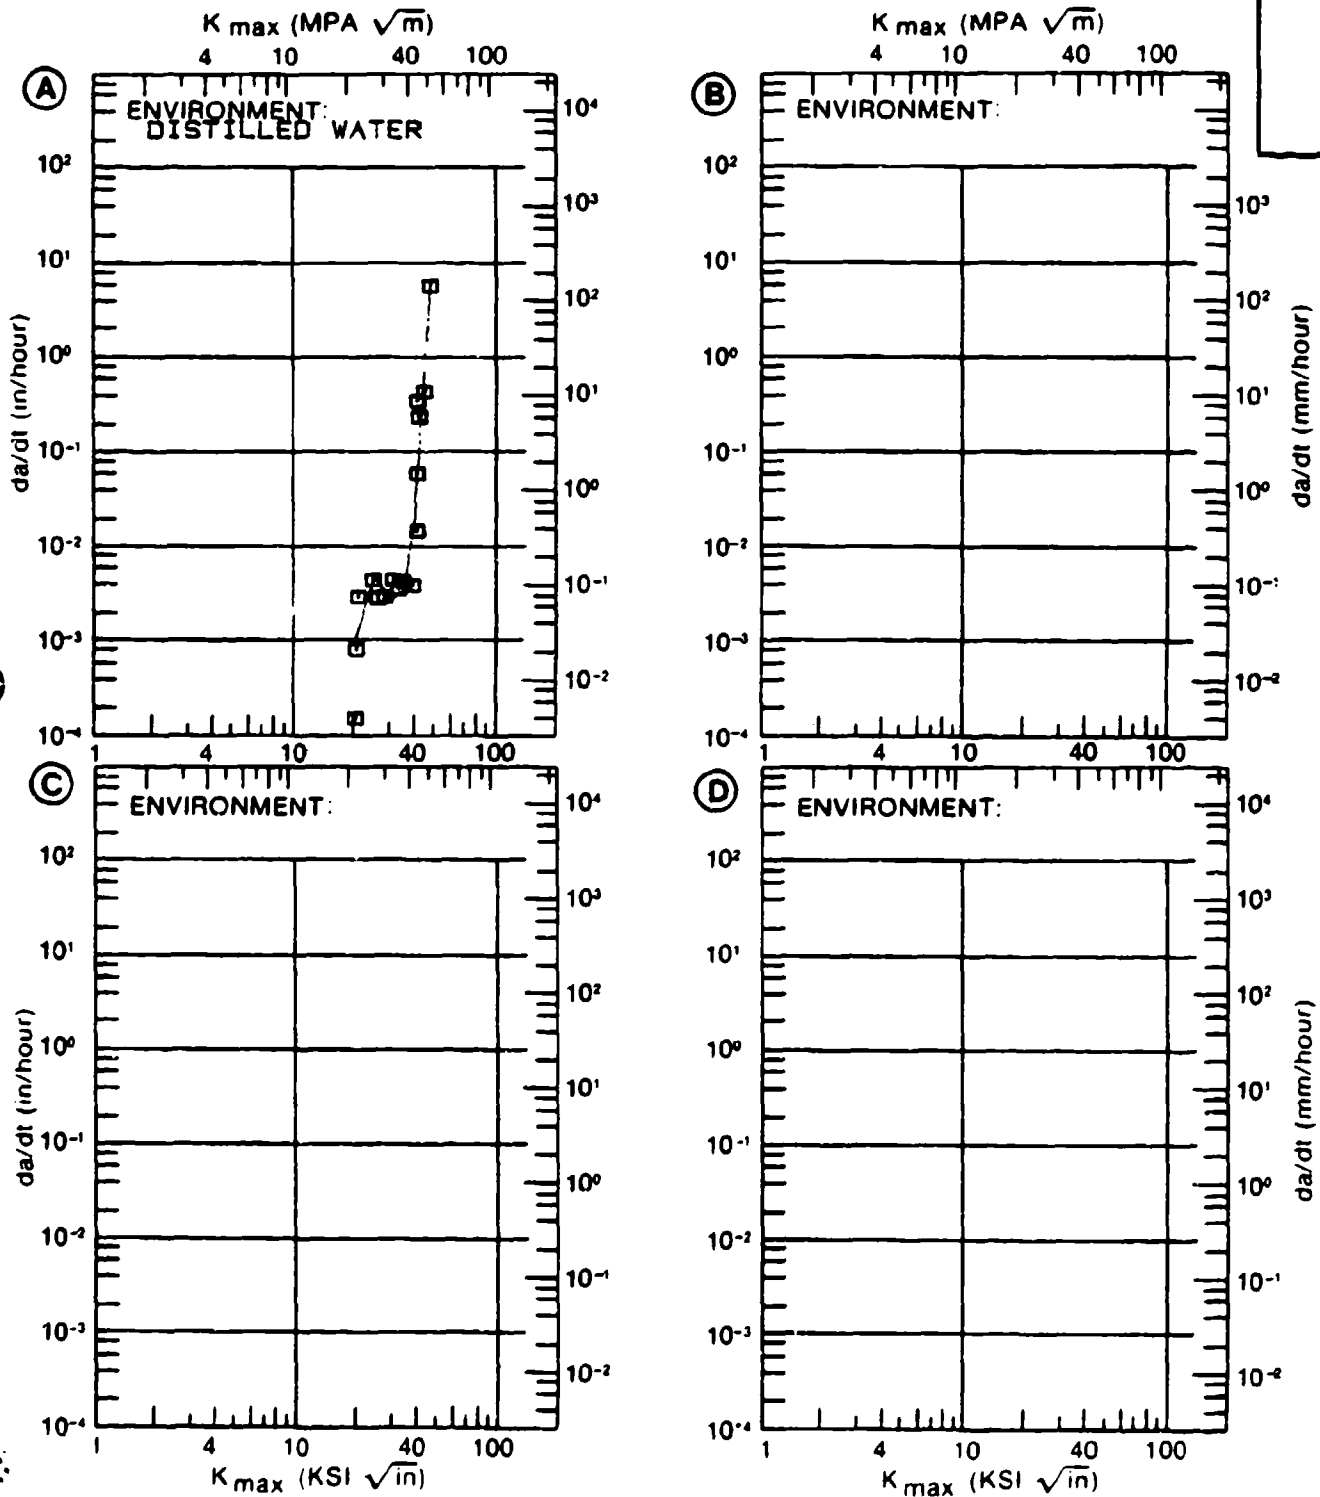


Figure 3.2.3.1

Table 3.2.3.2

CONDITION	PRODUCT FORM	THICK (IN)	TEMP (F)	SPEC YIELD STR (KSI)	ENVIRONMENT	WIDTH (IN)	SPECIMEN THICK (IN)	DESIGN (A-SG)	CRACK LENGTH (IN)	K(I SCC)	MEAN DEV	TEST TIME (MIN)	DATE REFER
1800F 1HR OG. P -100F 0 5HR. 500F 2+2 HR (COARSE GRAINED STRUCTURE)	P	0.56	R T	154.0	3.5 PCT NAACL	1.500	0.480	CANT*	119.00	82.00*		1969 74720	
1800F 1HR OG. P -100F 0 5HR. 1100F 2+2 HR (COARSE GRAINED STRUCTURE)	P	0.56	R T	173.0	3.5 PCT NAACL	1.500	0.480	CANT*	23.00	15.00		1969 74720	
1800F 1HR OG. P -100F 0 5HR. 500F 2+2 HR (FINE GRAINED STRUCTURE)	P	0.56	R T	196.0	3.5 PCT NAACL	1.500	0.480	CANT*	111.00	97.00*		1969 74720	
1800F 1HR OG. P -100F 0 5HR. 1100F 2+2 HR (FINE GRAINED STRUCTURE)	P	0.56	R T	232.0	3.5 PCT NAACL	1.500	0.480	CANT*	30.00	20.00		1969 74720	
2000F 1HR OG. B -100F 0 5HR. 1400F 2+2 HR	B	3.00	R T	150.0	3.5 PCT NAACL	1.500	0.480	CANT*	116.00	80.00*		1969 76136	
2000F 1HR OG. B -100F 0 5HR. 500F 2+2HR	B	3.00	R T	169.0	3.5 PCT NAACL	1.500	0.480	CANT*	200.00	109.00*		1969 76136	
2000F 1HR OG. B -100F 0 5HR. 700F 2+2 HR	B	3.00	R T	180.0	3.5 PCT NAACL	1.500	0.480	CANT*	160.00	50.00		1969 76136	
2000F 1HR OG. B -100F 0 5HR. 800F 2+2 HR	B	3.00	R T	207.0	3.5 PCT NAACL	1.500	0.480	CANT*	70.00	40.00		1969 76136	
2000F 1HR OG. B -100F 0 5HR. 900F 2+2 HR	B	3.00	R T	214.0	3.5 PCT NAACL	1.500	0.480	CANT*	56.00	35.00		1969 76136	
2000F 1HR OG. B -100F 0 5HR. 1100F 2+2 HR	B	3.00	R T	221.0	3.5 PCT NAACL	1.500	0.480	CANT*	43.00	10.00		1969 76136	

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(K(I SCC)/TYS)SQUARED

Table 3.2.3.2 (Continued)

CONDITION	--PRODUCT--		TEST SPEC		STAINLESS STEEL	AFC	77	K(IISCC)	SPECIMEN		CRACK	K(IISCC)	MEAN	DEV	TEST	DATE	REFER
	FORM	THICK	TEMP	DR					WIDTH	THICK							
	(IN)	(F)	(RBI)	ENVIRONMENT	(IN)	(IN)	(RBI)	(IN)	(IN)	(IN)	(RBI)	(IN)	(IN)	(MIN)			
2000F 1HR 0G, B -100F 0.5HR 500F 2+2HR + 10 PCT CM, 1000F	B	3 00	R.T.	252.0 3.5 PCT NAACL	1.500	0.480	CANT*	----	60.00	30.00	----	1969	76136				
2000F 1HR 0G, B -100F 0.5HR 500F 2+2HR + 10 PCT CM, 700F	B	3 00	R.T.	277.0 3.5 PCT NAACL	1.500	0.480	CANT*	----	106.00	90.00	----	1969	76136				
2000F 1HR 0G, B -100F 0.5HR 500F 2+2HR + 20 PCT CM, 700F	B	3 00	R.T.	297.0 3.5 PCT NAACL	1.500	0.480	CANT*	----	107.00	48.00	----	1969	76136				
2100F 1HR, FC TO 1900F HOLD 1HR, 0G, -100F 4HR, 500F 2+2 HR	F	10 00	R.T. L-T	165.8 3.5 PCT NAACL	20	0.500	MB	* 0.400	108.00	> 10.00	----	1973	87360				
2100F 1HR, FC TO 1900F HOLD 1HR, 0G, -100F 4HR, 500F 2+2 HR	F	10 00	R.T. T-L	164.6 3.5 PCT NAACL	13	0.500	MB	* 0.400	110.00	> 10.00	----	1973	87360				

Table 3.3.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
STAINLESS STEEL ALLOY AEC 77 (VAR) AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION		EDBLING		
	L-I	I-L	B-L	(NUMBER OF SPECIMENS)	
1700F 1HR.00 2100F 1HR. MOVED TO FCC AT 1933F. WELD 1HR.00. -100F 24HR. 900F. 2+2HR	48.6 ± 3.1 (7)	50.8 ± 1.3 (7)	-----		
2100F 1HR. MOVED TO FCC AT 1900F. WELD 1HR.00. -100F 4HR. 500F 2+2HR	110.9 ± 4.9 (2)	108.0 ± 5.7 (2)	-----		

Table 3.4.3.1

CONDITION	--PRODUCT--		TEST SPEC YIELD TEMP OR STR (F) (KSI)	ENVIRONMENT	STAINLESS STEEL AM 355		WIDTH (IN) W	SPECIMEN		CRACK LENGTH K(O) (IN) (ABI+SQRT IN)	K (ISCC)	MEAN DEV	TEST TIME (MIN)	DATE REFER
	THICK (IN)	FORM			THICK (IN)	DESIGN (IN) (S)		STAN DEV						
H00 SCT1000	B	2.25	R.T.	163.2 3.5 PCT NACL	1.900	0.480	CANT	117.00	117.00*				> 30000	1971 84333
SCT 850	P	1.13	R.T.	T-L 152.3 INDUSTRIAL ATM	2.000	1.000	CT	48.00	45.00					1973 86688
SCT 850	P	1.13	R.T.	T-L 152.3 SEACAST ATM	2.000	1.000	CT	48.00	24.00					1973 86688
SCT 850	P	1.13	R.T.	T-L 152.5 20PCT NACL	2.000	1.000	CT	48.00	8.00					1973 86688
SCT 850	B	2.25	R.T.	--- 180.0 3.5 PCT NACL	1.900	0.480	CANT	59.20	32.50				> 30000	1971 84333
SCT 850	B	2.00	R.T.	T-L 190.3 INDUSTRIAL ATM	2.000	1.000	CT	36.60	18.00					1973 86688
SCT 850	B	2.00	R.T.	T-L 190.3 SEACAST ATM	2.000	1.000	CT	36.60	18.00					1973 86688
SCT 850	B	2.00	R.T.	T-L 190.3 20 PCT NACL	2.000	1.000	CT	36.60	6.00					1973 86688
SCT1000	P	1.13	R.T.	T-L 169.7 INDUSTRIAL ATM	2.000	1.000	CT	104.70	99.00					1973 86688
SCT1000	P	1.13	R.T.	T-L 169.7 SEACAST ATM	2.000	1.000	CT	104.70	52.00					1973 86688
SCT1000	P	1.13	R.T.	T-L 169.7 20 PCT NACL	2.000	1.000	CT	104.70	37.00					1973 86688
SCT1000	B	2.25	R.T.	--- 171.2 3.5 PCT NACL	1.900	0.480	CANT	88.40	88.40*				> 30000	1971 84333
SCT1000	B	2.00	R.T.	T-L 172.4 INDUSTRIAL ATM	2.000	1.000	CT	70.00	66.00					1973 86688
SCT1000	B	2.00	R.T.	T-L 172.4 SEACAST ATM	2.000	1.000	CT	70.00	35.00					1973 86688
SCT1000	B	2.00	R.T.	T-L 172.4 20 PCT NACL	2.000	1.000	CT	70.00	28.00					1973 86688

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(KISCC/TYS)SQUARED

Table 3.5.3.1

CONDITION	--PRODUCT--		TEST SPEC	YIELD STR (KSI)	ENVIRONMENT	---SPECIMEN---		WIDTH (IN)	THICK (IN)	DESIGN (IN)	CRACK		STAN DEV	TEST TIME (MIN)	DATE REFER
	FORM	THICK (IN)				LENGTH (IN)	K (IBCC)				K (IBCC)	MEAN			
H 900	B	2.25	R.T.	200.5	3.5 PCT NAACL	1.500	0.480	CANT	---	30.20	12.50	---	>	42000	1971 84333
H1000	B	2.25	R.T.	178.9	3.5 PCT NAACL	1.500	0.480	CANT	---	40.10	31.00	---	>	36000	1971 84333

Table 3.6.3.1

CONDITION	---PRODUCT---		TEST TEMP OR (F)	YIELD STRENGTH (KSI)	ENVIRONMENT	STAINLESS STEEL AM 364		CRACK LENGTH (IN)	K (ISCC)	MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
	FORM	THICK (IN)				WIDTH (IN)	THICK (IN)						
H 850	F	3 00	R T	183 3	3 5 PCT NAACL	1.500	0.480	CANT	131.00	93.00*		> 60000	1971 84333
H 950	F	3 00	R T	186 7	3 5 PCT NAACL	1.500	0.410	CANT	128.00	128.00*		> 60000	1971 84333

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(KI/BSQ/TS/SQUARED)

Table 3.7.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
STAINLESS STEEL ALLOY CUSTOM 435 AT ROOM TEMPERATURE

CONDITION/MT	MEAN K _{IC} ± STANDARD (AS ₁ SORT(IN)) DEVIATION		EDS/INS	
	L-I	I-I	L-I	I-I
1500F 1HR. 00. 950F 4HR. AC	72.1 ± 7.0 (2)	---	---	8-I
1500F 1HR. 00. 900F 4HR. AC	46.2 ± 3.3 (3)	---	---	---

Table 3.7.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL CUSTOM 433

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: LAB AIR AT R.T.

CONDITION/MT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 9 10 20 50 100	
H1040	FORGING	0.10	10.00-30.00		2.78
H1050	FORGING	0.30	10.00-30.00		3.72

Table 3.7.1.3

FATIGUE CRACK GROWTH RATE AT DELTA K LEVELS OF THE STRESS-INTENSITY FACTOR
 STAINLESS STEEL CUSTOM 409

TEST CONDITIONS

SPECIMEN ORIENTATION 1-1

ENVIRONMENT: LAB AIR AT R.T.

CONDITION/HIT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)				
				2.5	5	10	20	50	100
H1000	FORGING	0.10	10.00						25.0
H1000	FORGING	0.10	20.00				3.00		
H1000	FORGING	0.10	20.00-30.00				2.58		

Table 3.7.2.1

CONDITION	--PRODUCT--		STAINLESS STEEL		CUSTOM 439		K (IC)		YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	SPECIMEN DESIGN	CRACK LENGTH (IN)	2.5% CRACK LENGTH (K(IC)/TYS)±2 (IN)	K (IC) MEAN (KSI±SDPT IN)	K (IC) STAN DEV	DATE	REFER
	FORM	THICK (IN)	THICK (IN)	THICK (IN)	M	B	A											
1500F 1HR.DG. 950F 4HR.AC	F	4.00	R.T.	L-T	1.500	0.480	N8	0.310	0.25	77.60	72.1/	7.8	77934					
1500F 1HR.DG. 900F 4HR.AC	F	4.00	R.T.	L-T	1.500	0.480	N8	0.320	0.07	47.70	44.2/	3.3	77934					

TABLE 3.7.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.7.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL CUSTOM 455
CONDITION: H1000
ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.30		
DELTA K A:	10.07	281			
DELTA K B:	12.71		1.04		
MIN C:					
D:					
	13.00	.699	1.10		
	16.00	1.39	1.99		
	20.00	2.78	3.72		
	25.00	4.91			
	30.00	6.90			
DELTA K A:	32.83	8.14			
DELTA K B:	23.86		5.31		
MAX C:					
D:					
ROOT MEAN SQUARE		11.51	2.74		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	3	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: H1000
 FORM: 2.50" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 10.0 - 30.0 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 195.0 KSI
 ULT. STRENGTH: 204.4 KSI
 SPECIMEN THK: 0.750"
 SPECIMEN WIDTH: 2.100"
 REFERENCES: R1004

STAIN.
STEEL

CUSTOM
455

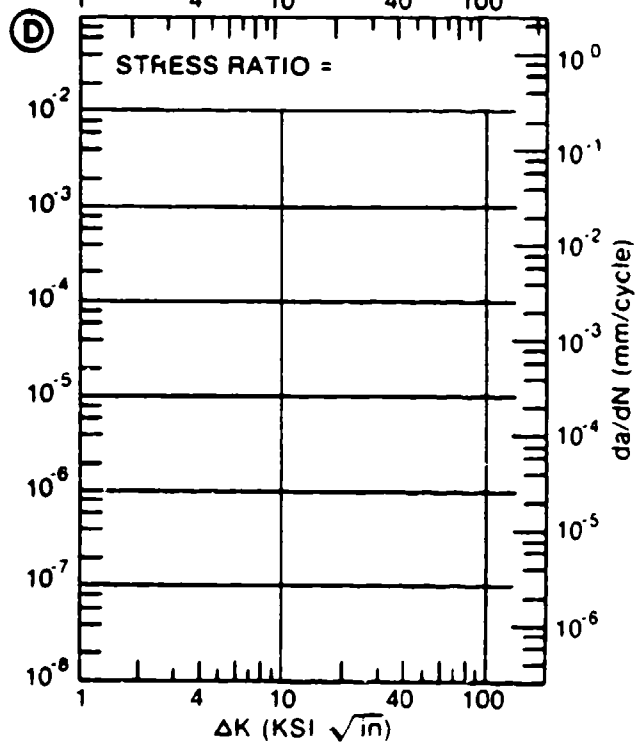
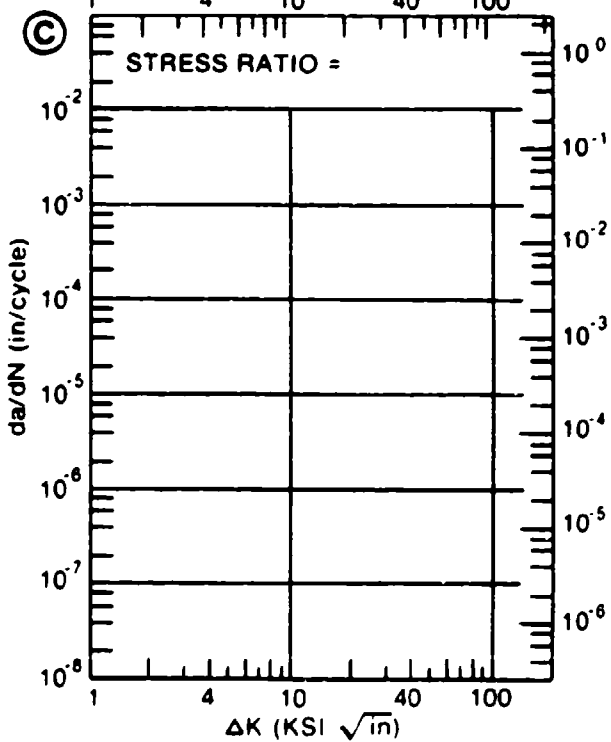
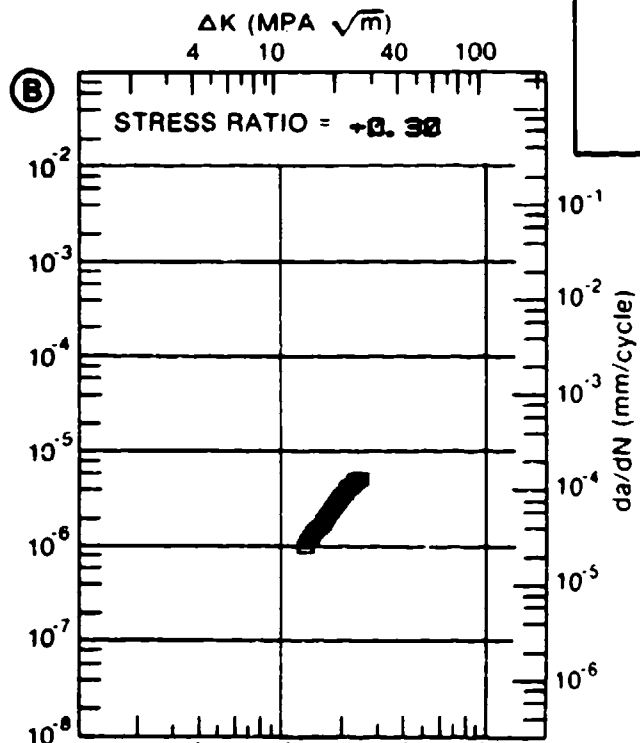
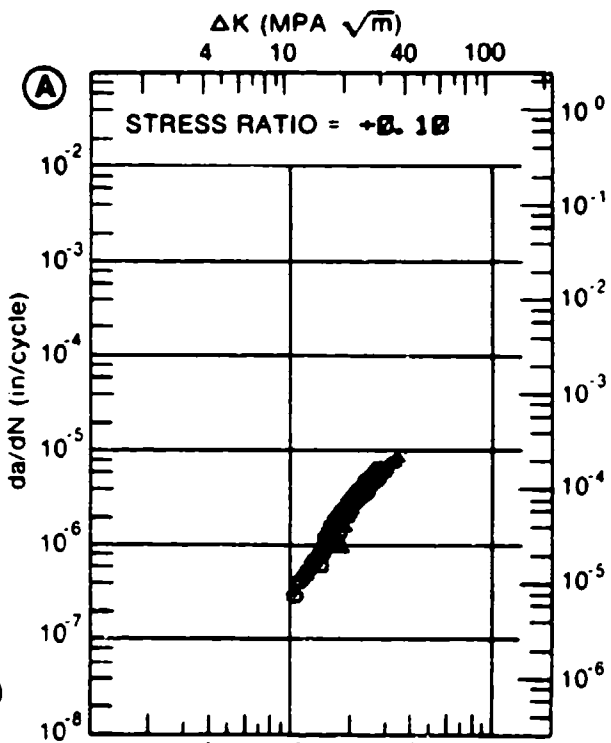


Figure 3.7.3.1

TABLE 3.7.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.7.3.2 INDICATING EFFECT
OF FREQUENCY

MATERIAL: STAINLESS STEEL CUSTOM 455
CONDITION: H1000
ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		F(HZ)= 5.0	F(HZ)= 10.0	F(HZ)= 20.0	
DELTA K MIN	A: 62.02	39.7			
	B: 25.12		4.98		
	C: 12.70			.739	
	D:				
	13.00			.703	
	16.00			1.04	
	20.00			3.00	
	25.00			3.70	
	30.00		7.09		
	35.00		10.0		
40.00		13.9			
50.00		25.0			
60.00					
70.00	68.9				
DELTA K MAX	A: 76.71	82.1			
	B: 56.40		35.0		
	C: 25.96			3.16	
	D:				
ROOT MEAN SQUARE		9.70	9.22	22.29	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8			1	
RATIO	0.8-1.25	1	1	1	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: H1000
 FORM: 2.50" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 105.0 KSI
 ULT. STRENGTH: 204.4 KSI
 SPECIMEN THK: 0.750"
 SPECIMEN WIDTH: 2.100"
 REFERENCES: R1004

STAIN.
 STEEL

CUSTOM
 455

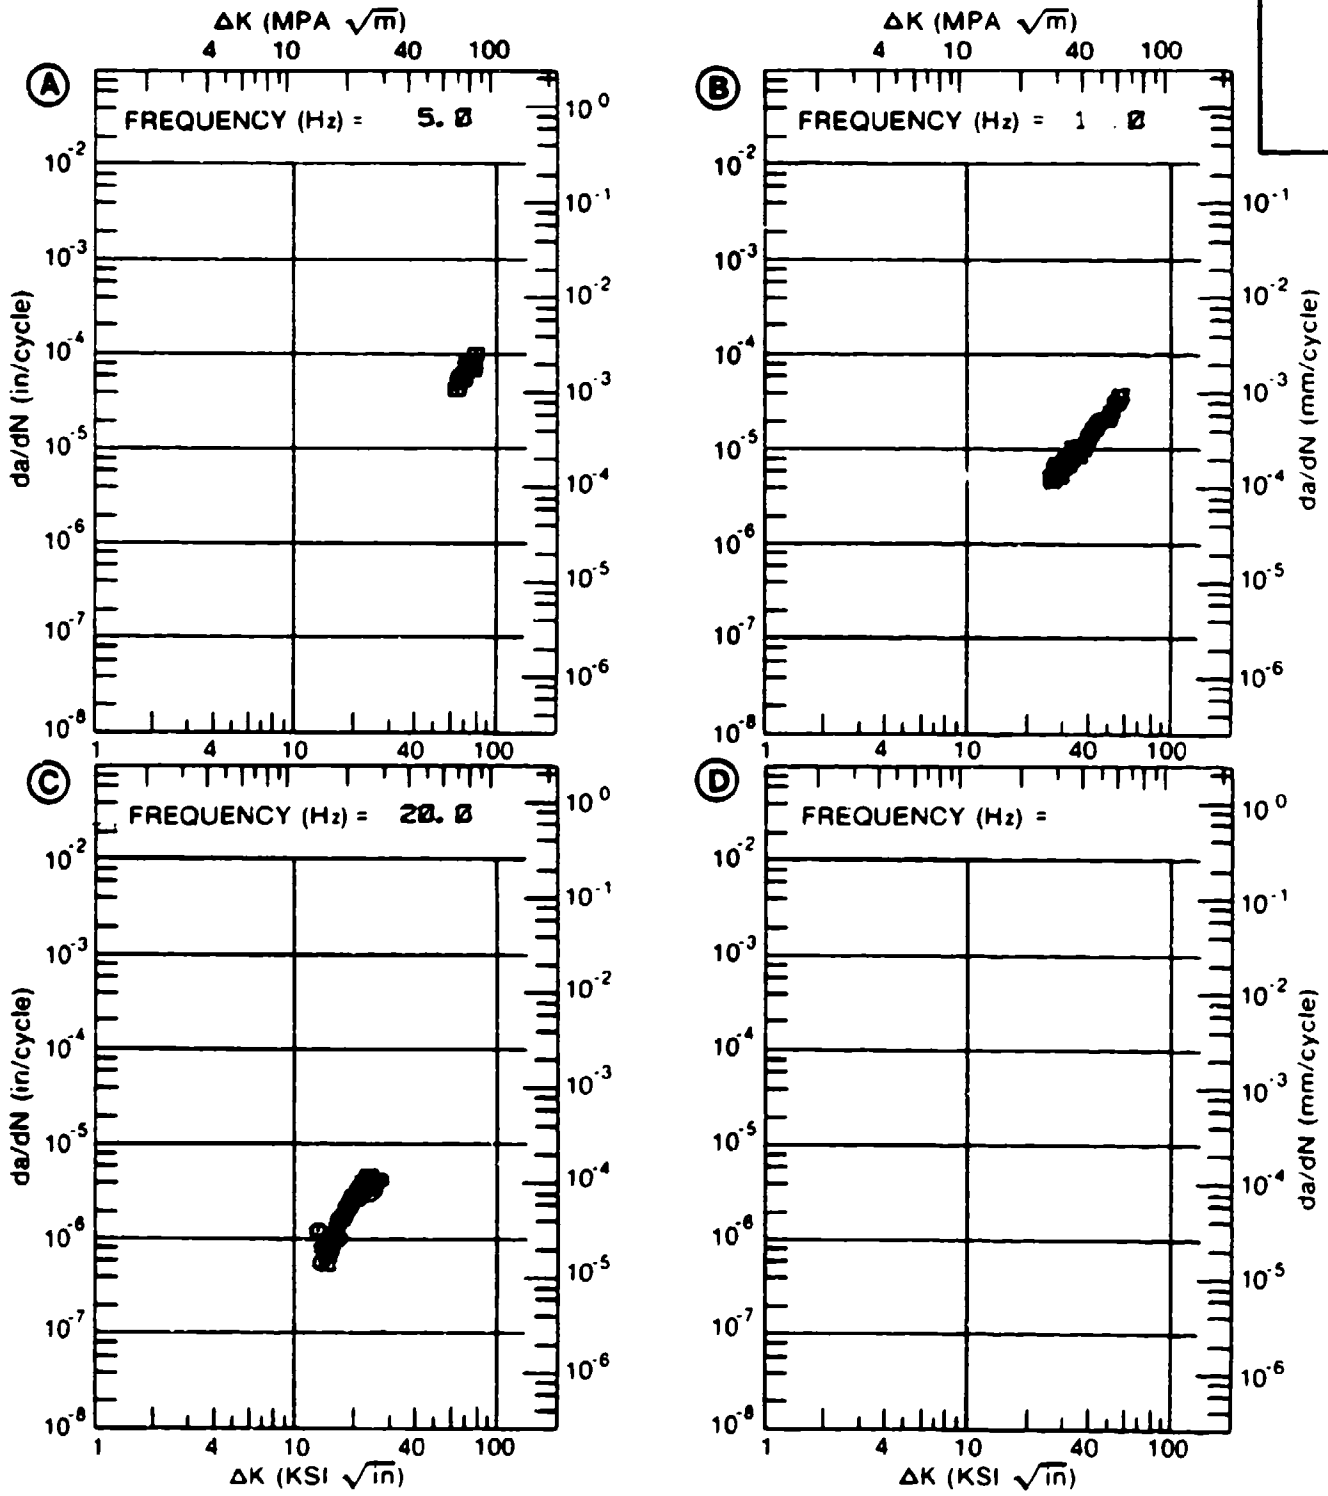


Figure 3.7.3.2

TABLE 3.7.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 3.7.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL CUSTOM 455
CONDITION: H1000

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E= R. T. LAB AIR	E= 100F AIR		
DELTA K MIN	A: 10.09	.256		
	13.00	.828		
	16.00	1.43		
	20.00	2.58		
	25.00	4.75		
DELTA K MAX	A: 27.10	6.32		

ROOT MEAN SQUARE 13.93 0.00
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 3
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: H1000
 FORM: 2.50" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 20.0 - 30.0 HZ

YIELD STRENGTH: 195.0 - 205.0 KSI
 ULT. STRENGTH: 204.4 KSI
 SPECIMEN THK: 0.750"
 SPECIMEN WIDTH: 2.100"
 REFERENCES: RI004

STAIN.
STEEL

CUSTOM
453

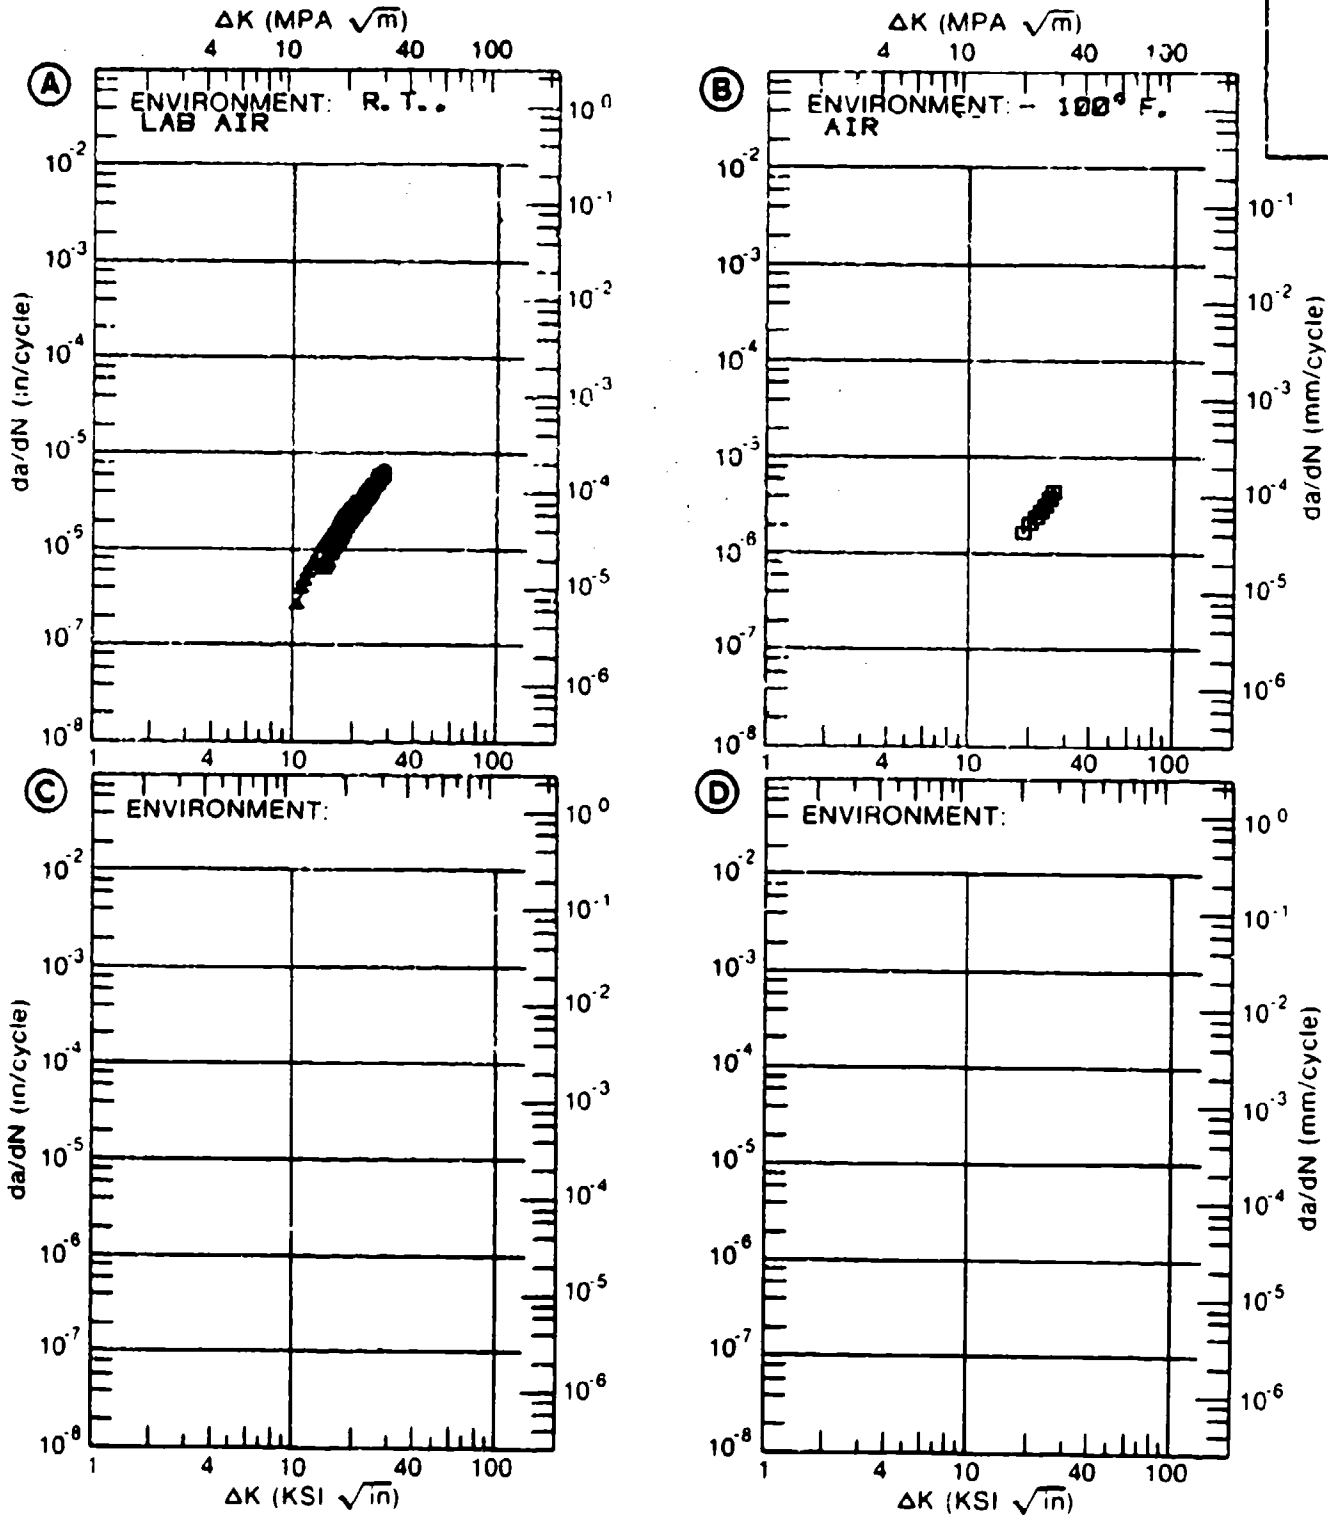


Figure 3.7.3.3

Table 3.7.3.4

CONDITION	STAINLESS STEEL CUSTOM 435 K(IISCC)																
	FORM	THICK (IN)	TEST TEMP (F)	SPEC OR STR (KSI)	YIELD (KSI)	ENVIRONMENT	SPECIMEN		WIDTH (IN)	THICK (IN)	DESIGN (KSI)	CRACK LENGTH (IN)	K(I) (KSI*SQRT IN)	K(IISCC) MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
							W	B									
H 500	F	4 00	R T	---	255.0	3.5 PCT NACL	1.500	0.500	CANT	---	62.00	60.00	60.00	---	> 60000	1969 77934	
H 550	F	4 00	R T	---	246.0	3.5 PCT NACL	1.500	0.480	CANT	---	72.10	72.10	72.10	---	> 60000	1971 84333	

Table 3.8.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
STAINLESS STEEL ALLOY PH13-8MO AT ROOM TEMPERATURE

CONDITION/HT	MEAN KIC ± STANDARD (KSI SQRT(IN)) DEVIATION	(NUMBER OF SPECIMENS)
ROD		
CONDITION/HT	\bar{K}_{Ic}	S_{Ic}
H 950	58.4 ± 6.5 (2)	69.4 ± 16.1 (4)
H1000	103.6 ± 4.8 (6)	96.2 ± 9.2 (4)
PLATE		
CONDITION/HT	\bar{K}_{Ic}	S_{Ic}
H1000	94.7 ± 3.6 (3)	---
FORGING		
CONDITION/HT	\bar{K}_{Ic}	S_{Ic}
ANNEALED	114.1 ± 13.7 (3)	99.6 ± 22.4 (6)
H 950	70.3 ± 16.0 (9)	---
H1000	101.6 ± 11.0 (12)	88.1 ± 17.1 (7)
EXTRUSION		
CONDITION/HT	\bar{K}_{Ic}	S_{Ic}
H1000	68.5 ± 5.5 (8)	66.2 ± 2.1 (6)

Table 3.8.1.1.1 (Continued)

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
STAINLESS STEEL ALLOY PH13-8GD AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (MSI SQR(TIN)) DEVIATION		(NUMBER OF SPECIMENS)
	L-I	I-I	
FORGED BAR			
AUSTENITE COND AND TRANSFORMED AT 38F. ACED 1013F	103.0 ± 19.4 (2)	89.6 ± 1.8 (2)	-----
H1000	114.2 ± 0.9 (2)	122.7 ± 3.0 (3)	-----
ROLLED BAR			
CONDITION/HT	L-I	I-I	S-I
H 950	66.9 ± 2.9 (3)	63.5 ± 1.7 (6)	74.1 ± 2.1 (3)
H1000	90.0 ± 7.1 (2)	75.0 ± 4.2 (2)	-----
H1050	103.1 ± 4.6 (3)	94.8 ± 7.8 (6)	92.2 ± 4.2 (2)

Table 3.8.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 STAINLESS STEEL PH13-8W

TEST CONDITIONS

SPECIMEN ORIENTATION: L-T ENVIRONMENT: DRY AIR AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
H1000	FORGED BAR	0.10	6.00				0.23	3.07	29.6	
H1000	FORGED BAR	0.70	6.00				0.58	4.17		
H1000	FORGED BAR	0.50	6.00				0.64	4.79		

Table 3.8.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL PH13-8MO

TEST CONDITIONS

SPECIMEN ORIENTATION: L-T

ENVIRONMENT: L.H.A.
AT - 65 F

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)						
					2.5	5	10	20	50	100	
EXTRUDED BAR					0.08	6.00	1.32	21.6			
H1000	EXTRUDED BAR	0.08	6.00		0.23	2.87					
H1000	ROLLED BAR	0.08	6.00		1.67						

Table 3.8.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL PH13-8W

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: L.H.A. AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K (LEVELS (KSI SQRT(IN)))	2.5	5	10	20	50	100
	EXTRUDED BAR	0.00	6.00					2.22	20.8	
	EXTRUDED BAR	0.30	6.00					2.98		
H1000	FORCED BAR	0.08	6.00					5.82		
H1000	FORCED BAR	0.30	6.00					4.70		
H1000	FORCED BAR	0.50	6.00			0.91	4.70			
H1000	BILLET	0.00	6.00			0.34	4.02			
H1000	EXTRUDED BAR	0.08	6.00			0.33	3.73	34.4		
H1000	EXTRUDED BAR	0.50	6.00			0.85	5.59			
H1000	ROLLED BAR	0.08	1.00			0.29	3.37			
H1000	ROLLED BAR	0.00	6.00			0.29	3.40			
H1000	ROLLED BAR	0.30	6.00			0.62	4.39			
H1000	ROLLED BAR	0.50	6.00			0.79	5.09			

Table 3.8.1.5

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 STAINLESS STEEL PH13-8MU

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: LAB AIR AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K (LEVELS (KSI SQRT(IN)))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
H1000	FORGING	0.10	1.00-10.00		9.44 31.9 127
H1000	BAR	0.02	1.00		31.6

Table 3.8.1.6

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL PH13-8PH

TEST CONDITIONS

SPECIMEN

ORIENTATION: L-T

ENVIRONMENT:

H.M.A.
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2.5	5	10	20	50	100
H1000	FORGED BAR	0.10	1.00		0.29	7.56	103			
H1000	FORGED BAR	0.30	1.00		0.81	11.3	129			
H1000	FORGED BAR	0.50	1.00		0.94	12.5				

Table 3.8.1.7

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL PH13-8ND

TEST CONDITIONS

SPECIMEN ORIENTATION: L-T

ENVIRONMENT: S.T.M. AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)						
					2.5	5	10	20	50	100	
	EXTRUDED BAR	0.08	1.00								2.85
H1000	EXTRUDED BAR	0.08	1.00				0.64	7.11			
H1000	ROLLED BAR	0.08	1.00					4.13			
H1000	ROLLED BAR	0.30	1.00				0.64	12.2			
H1000	ROLLED BAR	0.08	0.10					6.44			

Table 3.8.1.8

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL PH13-8MW

TEST CONDITIONS

SPECIMEN
ORIENTATION: T-LENVIRONMENT: DRY AIR
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (MSI SQRT(IN))	2.5	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
H1000	FORGED BAR	0.10	6.00				0.26	3.14	24.3		
H1000	FORGED BAR	0.30	6.00				0.42	4.17	37.1		
H1000	FORGED BAR	0.50	6.00				0.51	4.60			

Table 3.8.1.9

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL PH13-8PH

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: L.H.A.
AT R.T.

CONDITION/MT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)				
					2.5	5	10	20	50
H1000	BILLET	0.08	6.00		0.34	3.47	31.3		
H1000	ROLLED BAR	0.08	6.00			4.01			

Table 3.8.1.10

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL PH13-8ND

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: H.M.A.
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	30	100
					FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
H1000	FORGED BAR	0.10	1.00						6.71	108
H1000	FORGED BAR	0.30	1.00				0.54	9.37	215	
H1000	FORGED BAR	0.50	1.00				1.08	11.6	607	

Table 3.8.1.11

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL 7H13-8M0

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: S.T.M.
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SORT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
H1000	FORGED BAR	0.08	1.00		18.5
H1000	ROLLED BAR	0.08	1.00		0.28 6.43

Table 3.8.2.1

CONDITION	PH13-8ND		PH13-8ND		PH13-8ND		PH13-8ND		PH13-8ND		PH13-8ND		PH13-8ND		PH13-8ND		PH13-8ND		PH13-8ND							
	FORM	THICK (IN)	YIELD (KSI)	STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5* (K(I.C.)/TVS) (IN)	K(I.C.) MEAN (KSI)	STAN DEV (IN)	DATE	REFER	FORM	THICK (IN)	YIELD (KSI)	STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5* (K(I.C.)/TVS) (IN)	K(I.C.) MEAN (KSI)	STAN DEV (IN)	DATE	REFER
ANNEALED	F	3 00	R T	L-T	3 978	2 003	CT	2 073	0 66	103 80		1976	MC001	F	3 00	R T	L-T	3 978	2 003	CT	2 073	0 66	103 80		1976	MC001
		3 00			4 000	2 003	CT	2 043	0 52	92 12		1976	MC001		3 00			4 000	2 003	CT	2 043	0 52	92 12		1976	MC001
		3 00			3 997	1 996	CT	2 058	1 02	128 41		1976	MC001		3 00			3 997	1 996	CT	2 058	1 02	128 41		1976	MC001
		3 00			2 000	1 007	CT	1 026	0 94	126 90		1976	MC001		3 00			2 000	1 007	CT	1 026	0 94	126 90		1976	MC001
ANNEALED	F	3 00	R T	T-L	4 000	1 999	CT	2 057	0 83	119 40	114.1/19.7	1976	MC001	F	3 00	R T	T-L	3 999	1 996	CT	2 060	0 43	83 91		1976	MC001
		3 00			4 000	2 003	CT	2 035	1 08	132 91		1976	MC001		3 00			4 000	2 003	CT	2 035	1 08	132 91		1976	MC001
		3 00			3 999	1 998	CT	2 061	0 73	109 27		1976	MC001		3 00			3 999	1 998	CT	2 061	0 73	109 27		1976	MC001
		3 00			2 000	1 007	CT	1 025	0 76	113 30		1976	MC001		3 00			2 000	1 007	CT	1 025	0 76	113 30		1976	MC001
AUSTENITIC COND AND TRANSFORMED AT 36F, AGED 1015F	F8	2 20	R T	L-T	3 938	2 002	CT	2 008	0 36	79 44		1976	MC001	F8	2 20	R T	T-L	2 000	1 004	CT	1 005	0 33	78 36	99.6/22.4	1976	MC001
		2 20			2 000	1 004	CT	1 005	0 33	78 36		1976	MC001		2 20			2 000	1 004	CT	1 005	0 33	78 36		1976	MC001
		2 20			2 999	1 635	CT	1 577	0 76	114 70		1973	89836		2 20			2 999	1 635	CT	1 577	0 76	114 70		1973	89836
		2 20			3 001	1 636	CT	1 597	0 44	89 20	103.0/19.4	1973	89836		2 20			3 001	1 636	CT	1 597	0 44	89 20	103.0/19.4	1973	89836
AUSTENITIC COND AND TRANSFORMED AT 36F, AGED 1015F	F8	2 20	R T	T-L	3 001	1 638	CT	1 604	0 46	90 80		1973	89836	F8	2 20	R T	T-L	3 001	1 634	CT	1 587	0 43	88 30	89.6/1.8	1973	89836
		2 20			3 001	1 634	CT	1 587	0 43	88 30		1973	89836		2 20			3 001	1 634	CT	1 587	0 43	88 30	89.6/1.8	1973	89836
		2 20			2 000	1 000	CT	1 000	0 22	63 00		1972	84365		2 20			2 000	1 000	CT	1 000	0 22	63 00		1972	84365
		2 20			2 000	1 000	CT	1 000	0 16	59 80	58.4/6.5	1972	84365		2 20			2 000	1 000	CT	1 000	0 16	59 80	58.4/6.5	1972	84365
H 950	S	1 50	R T	L-T	2 000	1 000	CT	1 000	0 22	63 00		1972	84365	S	1 50	R T	T-L	2 000	1 000	CT	1 000	0 38	81 60		1972	84365
		1 50			2 000	1 000	CT	1 000	0 16	59 80		1972	84365		1 50			2 000	1 000	CT	1 000	0 17	54 30		1972	84365
		1 50			2 000	1 000	CT	1 000	0 18	56 70	69.4/16.1	1972	84365		1 50			2 000	1 000	CT	1 000	0 41	85 00		1972	84365
		1 50			2 000	1 000	CT	1 000	0 18	56 70	69.4/16.1	1972	84365		1 50			2 000	1 000	CT	1 000	0 18	56 70	69.4/16.1	1972	84365
H 950	F	8 00	R T	L-T	2 000	1 000	CT	1 000	0 13	47 00		1972	84365	F	8 00	R T	L-T	2 000	1 000	CT	1 000	0 13	47 00		1972	84365
		4 00			2 000	1 000	CT	1 000	0 40	83 90		1972	84365		4 00			2 000	1 000	CT	1 000	0 40	83 90		1972	84365
		8 00			2 000	1 000	CT	1 000	0 40	84 30		1972	84365		8 00			2 000	1 000	CT	1 000	0 40	84 30		1972	84365
		4 00			2 000	1 000	CT	1 000	0 39	83 60		1972	84365		4 00			2 000	1 000	CT	1 000	0 39	83 60		1972	84365
H 950	F	4 00	R T	L-T	2 000	1 000	CT	1 000	0 47	91 30		1972	84365	F	4 00	R T	L-T	2 000	1 000	CT	1 000	0 47	91 30		1972	84365
		4 00			2 000	1 000	CT	1 000	0 28	70 30		1972	84365		4 00			2 000	1 000	CT	1 000	0 28	70 30		1972	84365
		8 00			2 000	1 000	CT	1 000	0 19	58 20	70.3/16.0	1972	84365		8 00			2 000	1 000	CT	1 000	0 19	58 20	70.3/16.0	1972	84365
		4 00			2 000	1 000	CT	1 000	0 18	55 90	70.3/16.0	1972	84365		4 00			2 000	1 000	CT	1 000	0 18	55 90	70.3/16.0	1972	84365

Table 3.8.2.1 (Continued)

CONDITION	STAINLESS STEEL PH13-8MO				K(IIC)	K(IIC)				DATE	REFER		
	--(PRODUCT)-- FIRM	TEST SPECIMEN THICK TEMP (IN) (F)	YIELD STRENGTH (KSI)	WIDTH THICK (IN) (IN)		DESIGN (IN)	CRACK LENGTH (IN)	2.5* (K(IIC)/TYS)** (IN)	M(IIC) MEAN DEV (K(IIC)-SORT IN)			STAN DEV	
H 950	RR	2 25	R T	L-T	202.0	2.000	1.000	CT	1.077	0.25	64.20	1973	86688
		2 25			202.0	2.000	1.000	CT	1.069	0.30	70.00	1973	86688
		2 25			202.0	2.000	1.000	CT	1.040	0.27	66.40	1973	86688
H 950	NB	2 25	R T	T L	197.0	2.000	1.000	CT	1.060	0.24	60.90	1973	86688
		2 25			197.0	2.000	1.000	CT	1.049	0.25	62.80	1973	86688
		2 25			197.0	4.000	2.000	CT	2.071	0.26	63.60	1973	86688
		2 25			197.0	4.000	2.000	CT	2.028	0.28	66.20	1973	86688
		2 25			197.0	2.000	1.000	CT	1.030	0.26	64.00	1973	86688
		2 25			197.0	4.000	2.000	CT	1.996	0.26	63.40	1973	86688
H 950	RB	2 25	R T	S L	203.0	1.500	0.750	CT	0.780	0.33	73.80	1973	86688
		2 25			203.0	1.500	0.750	CT	0.738	0.35	76.40	1973	86688
		2 25			203.0	1.500	0.750	CT	0.797	0.32	72.20	1973	86688
H1000	S	1 50	R T	L-T	205.0	2.000	1.000	CT	1.000	0.71	109.00	1972	84365
		1 50			205.0	2.000	1.000	CT	1.000	0.58	98.30	1972	84365
		2 25			211.0	-----	-----	NB	-----	0.68	110.00	1972	84365
		2 25			211.0	-----	-----	NB	-----	0.59	103.00	1972	84365
		2 25			211.0	2.000	1.000	CT	1.000	0.60	103.00	1972	84365
H1000	S	1 75			219.0	-----	-----	CT	-----	0.63	110.00	1972	84365
		1 50	R T	T-L	205.0	2.000	1.000	CT	1.000	0.61	101.00	1972	84365
		1 50			205.0	2.000	1.000	CT	1.000	0.59	99.70	1972	84365
		2 25			213.0	2.000	1.000	CT	1.000	0.49	94.30	1972	84365
		2 25			214.0	2.000	1.000	CT	1.000	0.44	89.60	1972	84365
H1000	P	4 00	R T	L-T	201.0	3.501	0.990	CT	1.761	0.59	98.10	-----	84306
		4 00			201.0	3.501	0.978	CT	1.768	0.55	94.90	-----	84306
H1000	P	4 00	R T	T-L	198.0	3.500	0.990	CT	1.796	0.54	91.00	-----	84306
		4 00			198.0	3.500	0.990	CT	1.796	0.54	93.40	-----	84306
H1000	F	4 00	-	65	185.0	3.994	1.381	CT	1.941	0.21	33.80	1973	85836
		5 00			195.0	2.000	1.000	CT	1.030	0.14	46.90	1973	85836
H1000	F	8 00	R T	L-T	205.0	1.000	2.000	CT	1.000	0.43	89.10	1973	85034
		8 00			205.0	2.493	1.238	CT	1.232	0.65	104.60	1974	88136
		8 00			205.0	1.000	2.000	CT	1.000	0.56	97.30	1973	85034
		8 00			205.0	2.493	1.261	CT	1.188	0.58	98.60	1974	88136

Table 3.8.2.1 (Continued)

CONDITION	FORM		YIELD STRENGTH (KSI)	SPECIMEN		CRACK LENGTH (IN)	K(IIC) STAN DEV (KSI*SQRT IN)	K(IIC) MEAN (KSI)	DATE	REFER		
	THICK (IN)	WIDTH (IN)		THICK (IN)	DESIGN (IN)							
H1000	F	4 00	R T	L-T	2 000	NB	1 000	131 00	1972	84365		
		8 00			1 259	CT	1 226	99 50	1974	88136		
		4 00			2 000	NB	1 000	106 00	1972	84365		
		6 00			1 948	CT	0 986	100 00	1973	85034		
		6 00			1 997	CT	0 988	99 40	1973	85034		
		4 00			1 000	CT	1 000	99 80	1973	85036		
		4 00			1 000	CT	1 000	91 70	1973	85036		
		4 00			1 000	CT	1 000	104 00	161 6/ 11 0	1973	85036	
		4 00			3 000	1 630	CT	---	56 00	1974	90011	
		2 25		65	T-L	1 630	CT	---	53 00	54 5/ 2 1	1974	90011
H1000	F	2 75	R T	T-L	2 002	0 752	CT	1 008	0 43	79 50	1973	85857
		2 75			2 003	0 751	CT	0 990	0 34	73 00	1973	85857
		2 75			2 004	0 750	CT	1 013	0 37	75 60	1973	85857
		2 75			2 003	0 750	CT	1 002	0 39	78 20	1973	85857
		6 00			2 001	0 752	CT	0 986	0 61	98 50	1973	85034
		6 00			1 999	0 752	CT	0 982	0 51	90 70	1973	85034
		6 00			1 000	2 000	CT	1 000	121 00	68 1/ 17 1	1973	85034
		8 00			3 002	1 368	CT	1 499	86 40	1973	85836	
H1000	E	1 50			3 000	1 000	CT	---	0 15	52 00	1974	90011
		1 50		65	L-T	3 000	1 000	CT	---	50 00	1974	90011
		1 50			3 000	1 000	CT	---	48 00	30 0/ 2 0	1974	90011
H1000	E	1 50	R T	L-T	3 000	1 000	CT	---	0 21	61 00	1974	90011
		1 50			3 000	1 000	CT	---	66 00	1974	90011	
		1 50			3 000	1 000	CT	---	70 00	1974	90011	
		1 50			3 000	1 000	CT	---	61 00	1974	90011	
		1 50			3 999	1 413	CT	1 973	72 20	1973	85836	
		1 50			3 999	1 417	CT	2 018	76 70	1973	85836	
		1 50			3 000	1 000	CT	---	71 00	1974	90011	
		1 50			3 000	1 000	CT	---	70 00	68 5/ 3 5	1974	90011
H1000	E	1 50		65	T-L	3 000	1 000	CT	0 12	48 00	1974	90011
		1 50			3 000	1 000	CT	---	48 00	1974	90011	
		1 50			3 000	1 000	CT	---	50 00	48 7/ 1 2	1974	90011
H1000	E	1 50	R T	T-L	3 000	1 000	CT	---	0 26	67 00	1974	90011
		1 50			3 000	1 000	CT	---	67 00	1974	90011	
		1 50			3 000	1 000	CT	---	67 00	1974	90011	

Table 3.8.2.1 (Continued)

CONDITION	FORM	THICK (IN)	TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	SPECIMEN			K (IC)	K (IC) STAM	DATE	REFER
						WIDTH (IN)	THICK (IN)	DESIGN				
STAINLESS STEEL PH13-CMO												
K (IC)												
CRACK LENGTH (IN)												
2.5*												
K (IC)/TYS**												
K (IC) MEAN DEV												
(KSI)*SQRT (IN)												
A												
B												
M												
H1000	E	1.50	R T	T-L	208.0	3.000	1.000	CT	----	0.22	62.00	1974 90011
		1.50			208.0	3.000	1.000	CT	----	0.27	68.00	1974 90011
		1.50			208.0	3.000	1.000	CT	----	0.25	66.00	66 2/ 2.1 1974 90011
H1000	FB	4.00	- 65	L-T	210.0	2.006	0.998	CT	1.028	0.14	48.90	1973 89836
H1000	FB	1.00	R T	L-T	213.0	2.006	1.000	CT	1.052	0.69	113.50	1978 80009
		1.00			213.0	2.004	1.000	CT	1.051	0.71	114.80	114.2/ 0.9 1978 80009
H1000	FB	1.00	R T	T-L	216.0	2.003	1.001	CT	1.034	0.83	124.80	1978 80009
		1.00			216.0	2.004	1.003	CT	1.048	0.76	119.30	1978 80009
		1.00			216.0	2.003	1.001	CT	1.058	0.82	124.00	122.7/ 3.0 1978 80009
H1000	RB	1.50	R T	L-T	203.0	3.000	1.000	CT	----	0.54	93.00	1974 90011
		1.50			203.0	3.000	1.000	CT	----	0.43	85.00	90.0/ 7.1 1974 90011
H1000	RB	1.50	R T	T-L	203.0	3.000	1.000	CT	----	0.36	78.00	1974 90011
		1.50			203.0	3.000	1.000	CT	----	0.31	72.00	75.0/ 4.2 1974 90011
H1025	S	5.00	R T	L-T	200.0	----	----	NB	----	0.44	84.30	1972 84363
H1050	RB	2.25	R T	L-T	172.0	2.000	1.000	CT	1.019	0.91	103.90	1973 86688
		2.25			172.0	2.000	1.000	CT	1.018	0.81	98.20	1973 86688
		2.25			172.0	2.000	1.000	CT	1.034	0.97	107.30	103.1/ 4.6 1973 86688
H1050	RB	2.25	R T	T-L	178.0	2.000	1.000	CT	1.030	0.61	88.10	1973 86688
		2.25			178.0	4.000	2.000	CT	2.104	0.82	102.10	1973 86688
		2.25			178.0	4.000	2.000	CT	2.091	0.81	101.40	1973 86688
		2.25			178.0	2.000	1.000	CT	1.032	0.59	86.30	1973 86688
		2.25			178.0	4.000	2.000	CT	2.105	0.82	102.30	1973 86688
		2.25			178.0	2.000	1.000	CT	1.028	0.62	88.90	94.9/ 7.8 1973 86688
H1050	RB	2.25	R T	S-L	176.0	1.500	0.750	CT	0.762	0.64	89.20	1973 86688
		2.25			176.0	1.500	0.750	CT	0.781	0.73	93.20	92.2/ 4.2 1973 86688
MILL 1700F, LAB 1050F 4HR	F	5.00	- 65	L-T	193.0	2.996	1.500	CT	1.546	0.41	78.80	1973 89836

Table 3.8.2.1 (Continued)

CONDITION	STAINLESS STEEL PH13-8F0										K(1C)	CRACK LENGTH (IN)	CRACK 2.99 K(1C)/TYS)**2 (KSI*SQRT IN)	K(1C) STAN MEAN DEV (IN)	DATE	REFER
	--PRODUCT-- FORM	THICK (IN)	TEST SPECIMEN ORIENT	TEMP (F)	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	DESIGN	DESIGN						
MILL 1700F.LAB 1600F.LAB 4HR	F	5.00	-	65	L-T	195.0	2.008	1.000	CT	1.060	0.30	67.60		1973	85836	
MILL 1700F.LAB 1500F.LAB 4HR	F	5.00	-	65	L-T	195.0	2.006	0.999	CT	1.052	0.34	72.50		1973	85836	
RH 950	RB	1.50	R.T.		L-R	210.0	1.000	0.500	CT	----	0.18	57.00		1974	90011	
		1.50				210.0	1.000	0.500	CT	----	0.22	62.00		1974	90011	
		1.50				210.0	1.000	0.500	CT	----	0.21	61.00		1974	90011	
		1.50				210.0	1.000	0.500	CT	----	0.20	59.00	57.8/	2.2	1974	90011
RH 975	RB	1.50	R.T.		L-R	207.0	1.000	0.500	CT	----	0.25	66.00		1974	90011	
		1.50				207.0	1.000	0.500	CT	----	0.34	76.00		1974	90011	
		1.50				207.0	1.000	0.500	CT	----	0.30	68.00	70.0/	5.3	1974	90011
RH1000	RB	1.50	R.T.		L-R	205.0	1.000	0.500	CT	----	0.34	95.00		1974	90011	

TABLE 3.8.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL PH13-8MO

CONDITION:

ENVIRONMENT: R. T., L. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30		
DELTA K MIN	A: 13.43	.370			
	B: 10.60		.114		
	C:				
	D:				
	13.00		.463		
	16.00	.936	1.32		
	20.00	2.22	2.98		
	25.00	4.12	5.56		
	30.00	6.17	8.77		
	35.00	8.51	13.1		
	40.00	11.4	19.6		
	50.00	20.8			
	60.00	40.2			
DELTA K MAX	A: 61.76	45.5			
	B: 48.07		38.4		
	C:				
	D:				
ROOT MEAN SQUARE		8.38	7.23		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0		1		
(NP/NA)	>2.0				

CONDITION/HT:
 FORM: EXTRUDED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.0 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 201.0 KSI
 ULT. STRENGTH: 212.0 KSI
 SPECIMEN THK: 0.280"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 99579

STAIN.
 STEEL

PH13-8MO

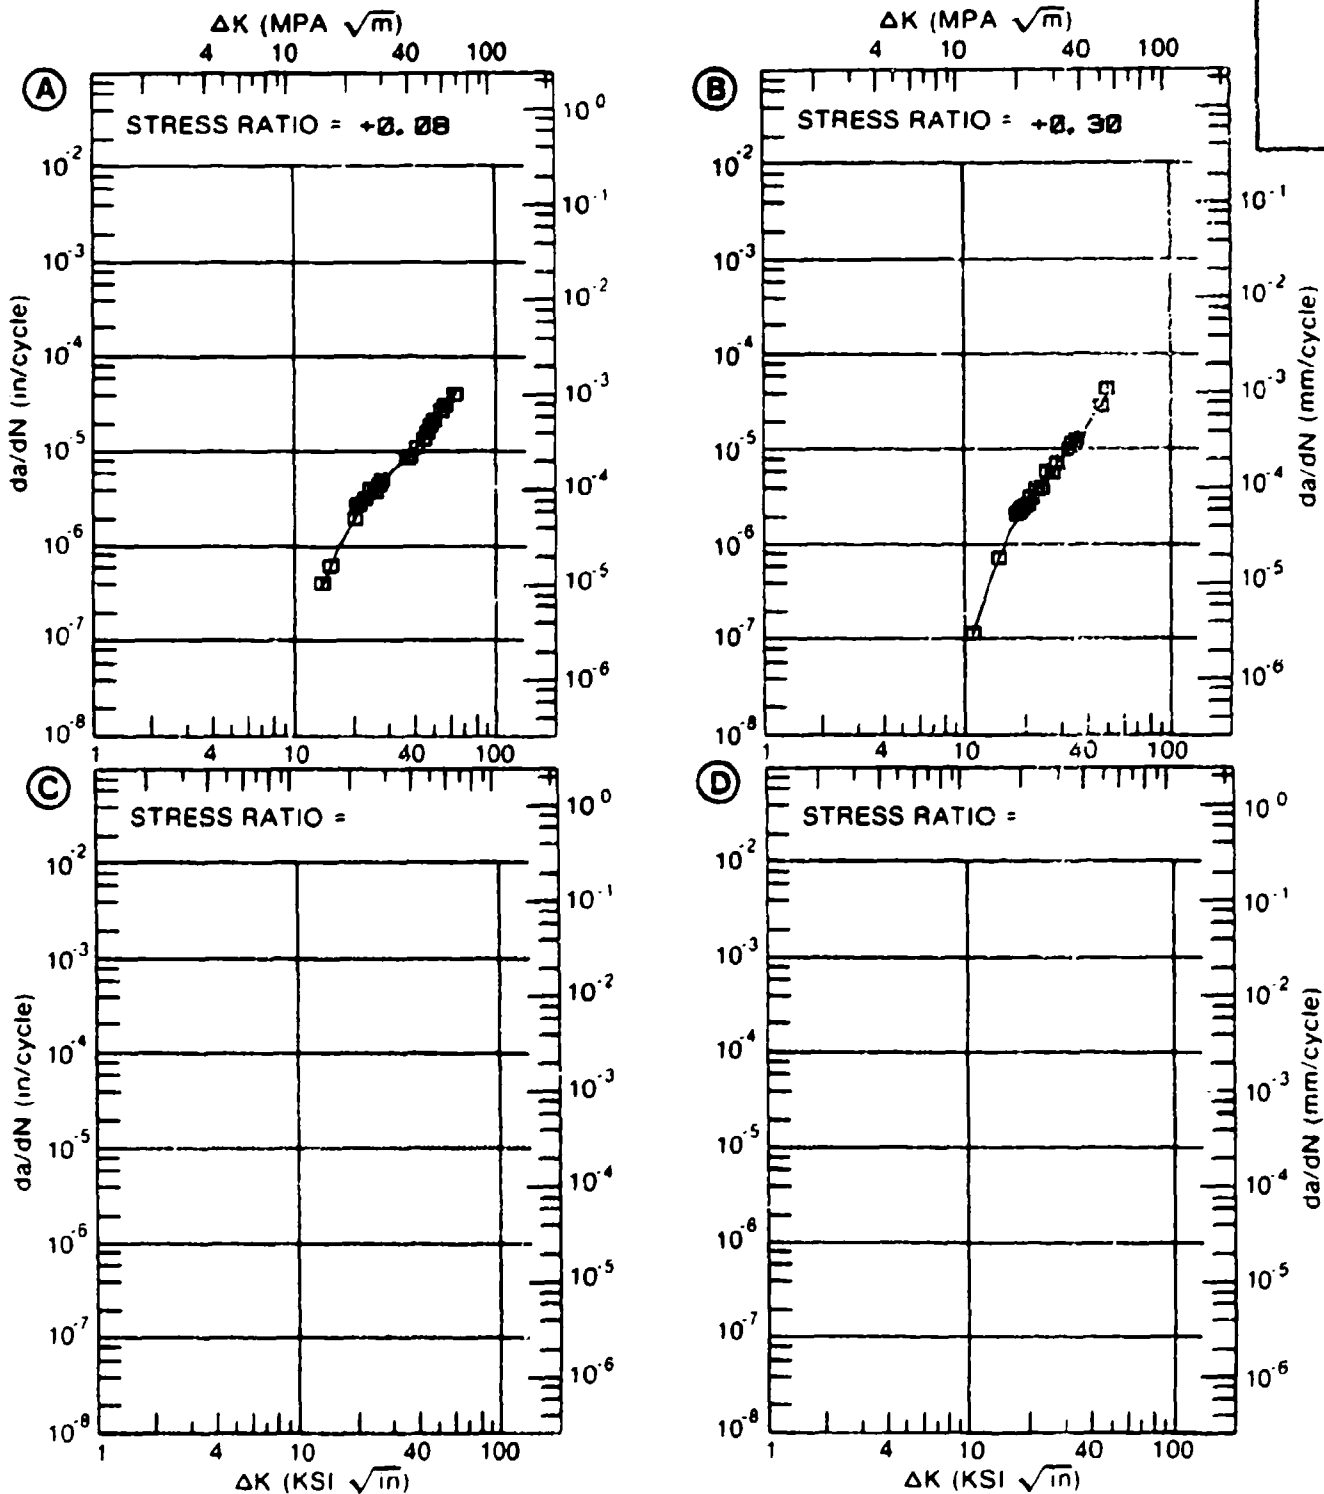


Figure 3.8.3.1

TABLE 3.8.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION:

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A. -6. OHZ	E=- 65 F L. H. A. -6. OHZ	E= R. T. S. T. W. -1. OHZ	
DELTA K MIN	A: 13.43	.370			
	B: 13.84		.259		
	C: 12.50			.148	
	D:				
	13.00			.211	
	16.00	.936	.531	.962	
	20.00	2.22	1.32	2.85	
	25.00	4.12	2.79	6.10	
	30.00	6.17	4.78	10.6	
	35.00	8.51	7.39	17.9	
	40.00	11.4	10.8	31.5	
	50.00	20.8	21.6		
	60.00	40.2	41.8		
DELTA K MAX	A: 61.76	45.5			
	B: 62.88		50.5		
	C: 42.46			42.5	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		8.38	7.09	6.15	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.2! 1.25-2.0 >2.0	1	1	1	

CONDITION/HT:
 FORM: EXTRUDED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 201.0 KSI
 ULT. STRENGTH: 212.0 KSI
 SPECIMEN THK: 0.250- 0.260"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 88578

STAIN.
 STEEL
 PH13-8MO

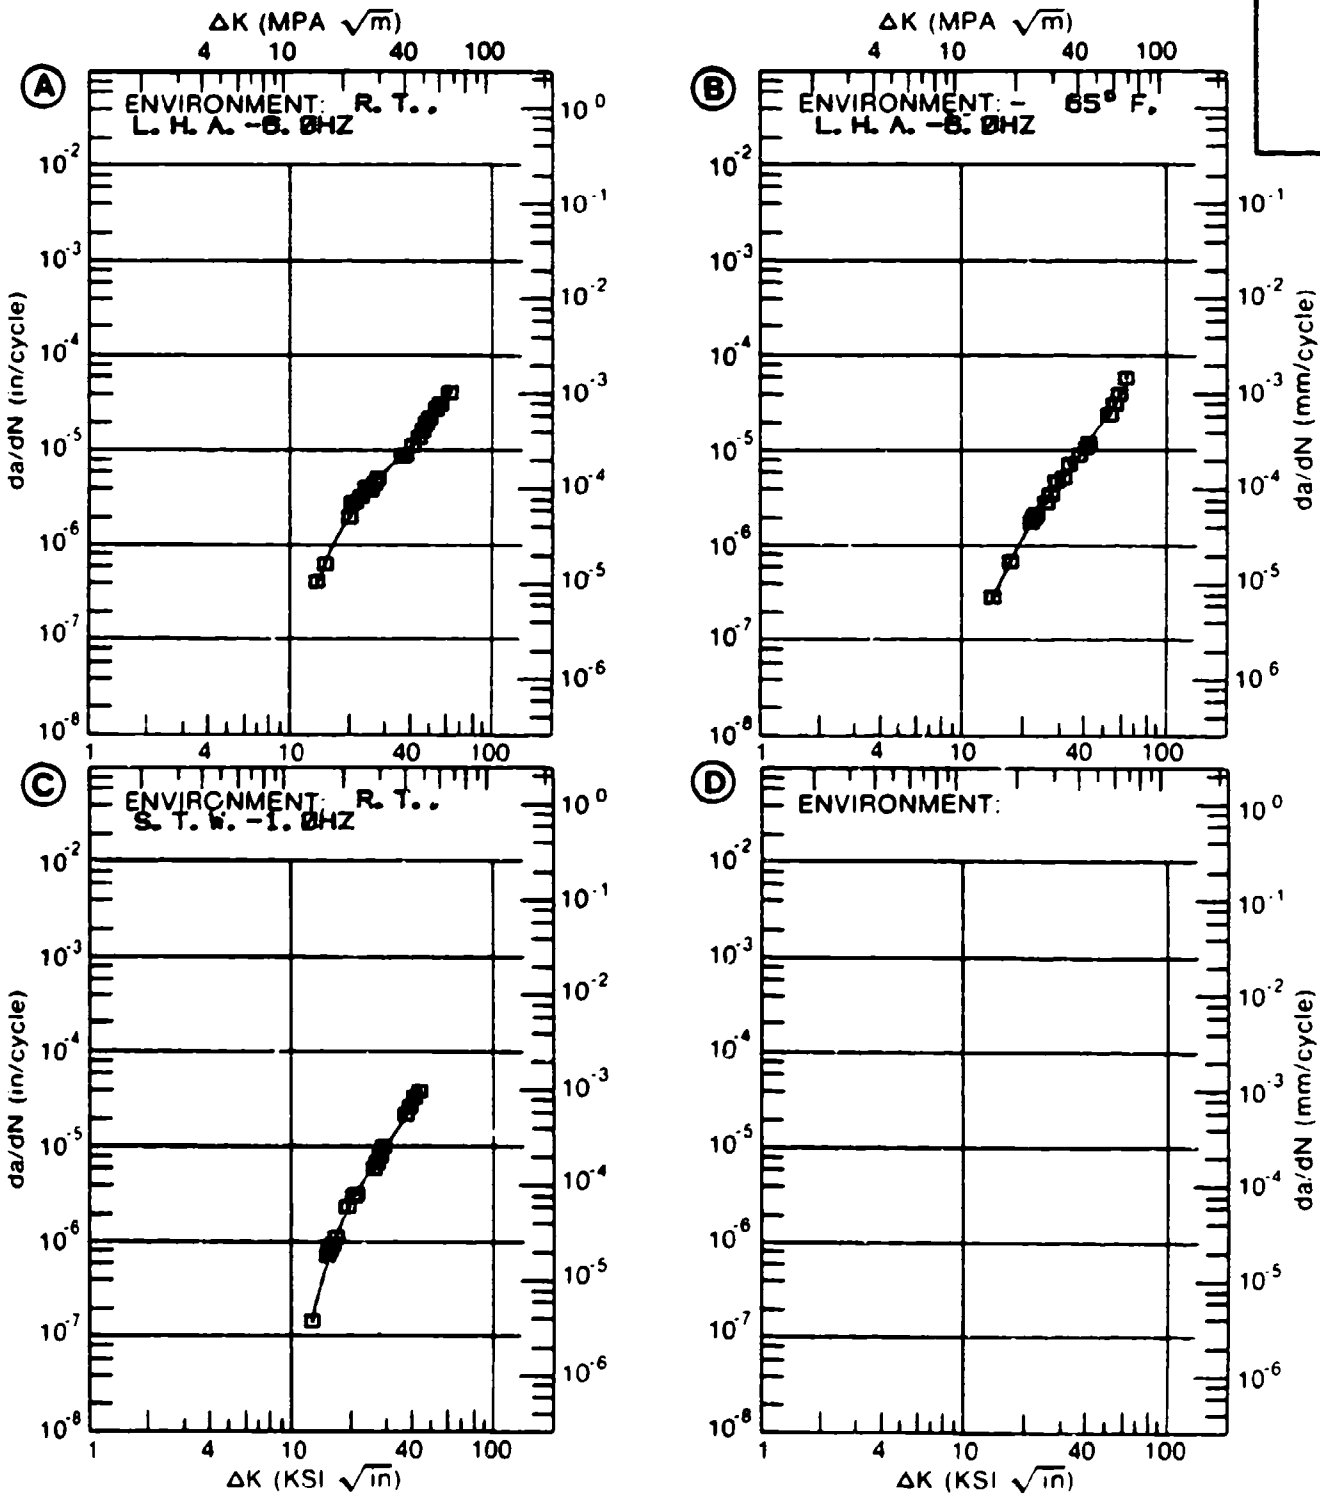


Figure 3.8.3.2

TABLE 3.8.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.3 INDICATING EFFECT
OF FREQUENCY

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000
ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		F(HZ)= 1.00			
DELTA K MIN	A: 22.06	5.28			
	B:				
	C:				
	D:				
	25.00	6.49			
	30.00	9.06			
	35.00	12.5			
	40.00	17.1			
	50.00	31.6			
DELTA K MAX	A: 56.54	46.7			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		1.97			
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: H1000
 FORM: 2.50" TH BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.02
 ENVIRONMENT: R.T., LAB AIR

YIELD STRENGTH: 205.0 KSI
 ULT. STRENGTH: 211.5 KSI
 SPECIMEN THK: 1.250"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 98136

STAIN.
 STEEL

PH13-8MO

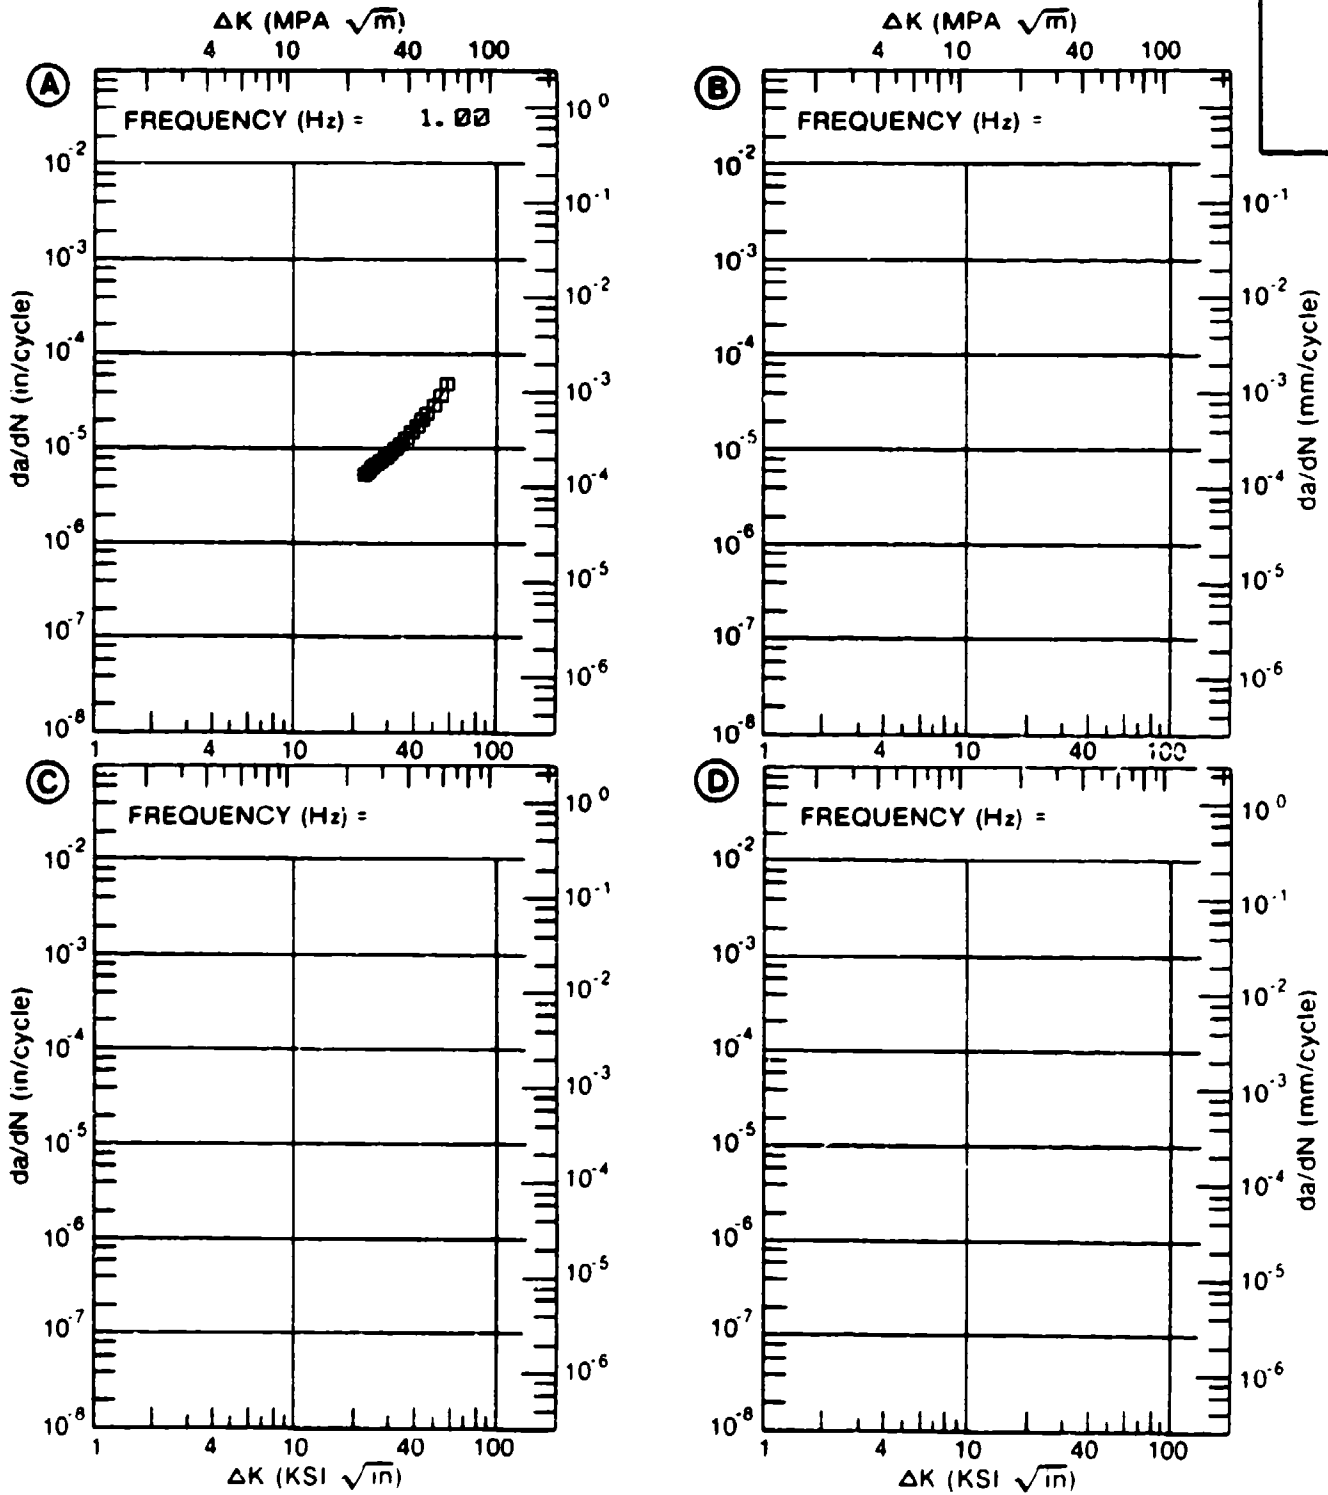


Figure 3.8.3.3

TABLE 3.8.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.4 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T.			
		L. H. A.			
DELTA K	A: 8.54	.20			
MIN	B:				
	C:				
	D:				
	9.00	.236			
	10.00	.341			
	13.00	.986			
	16.00	2.11			
	20.00	4.02			
	25.00	6.85			
	30.00	10.3			
	35.00	14.6			
DELTA K	A: 35.80	15.4			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 17.07
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: H1000
 FORM: 6.00" TH BILLET
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 191.0 KSI
 ULT. STRENGTH: 208.0 KSI
 SPECIMEN THK: 0.997"
 SPECIMEN WIDTH: 6.191"
 REFERENCES: 95837

STAIN.
 STEEL

PH13-8MO

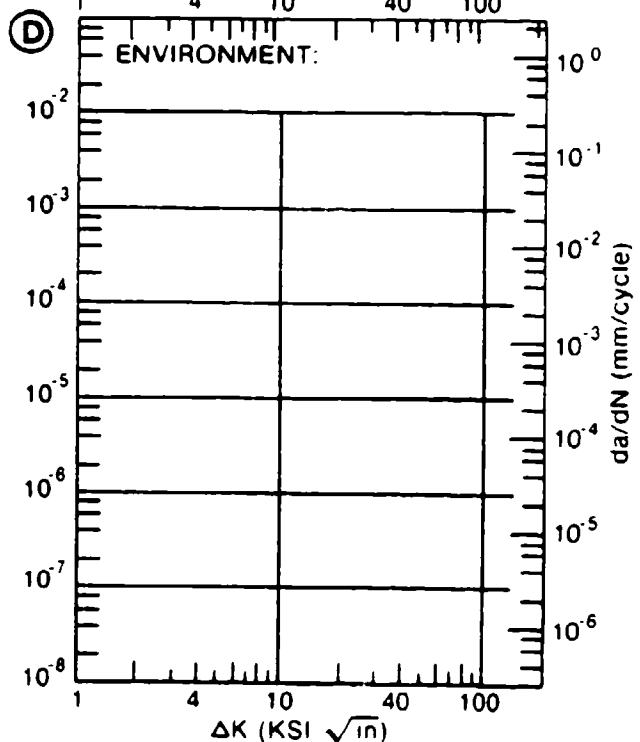
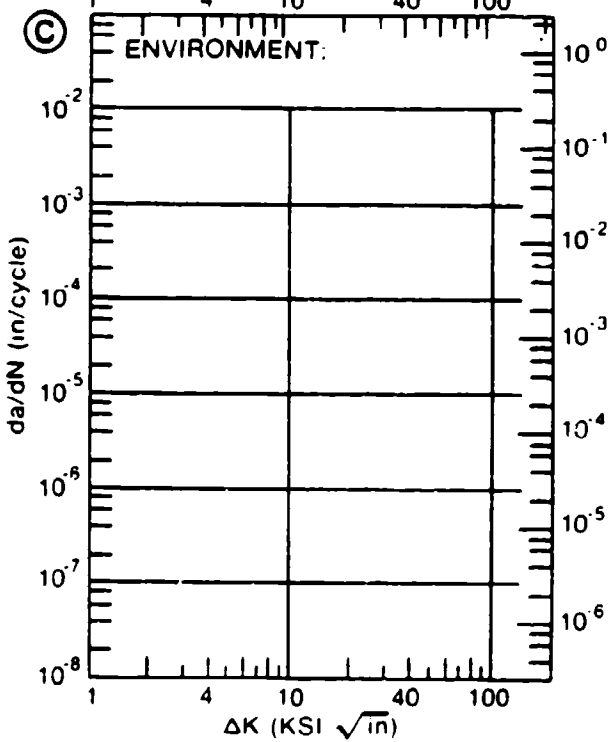
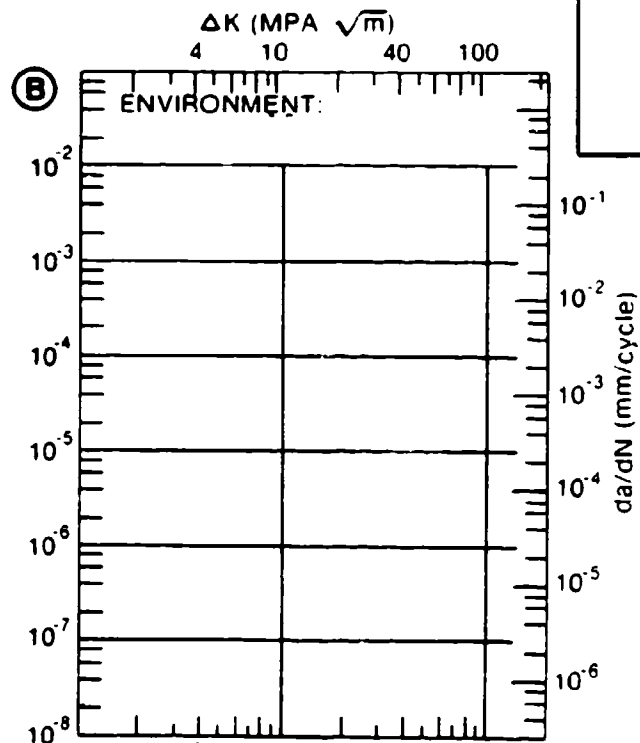
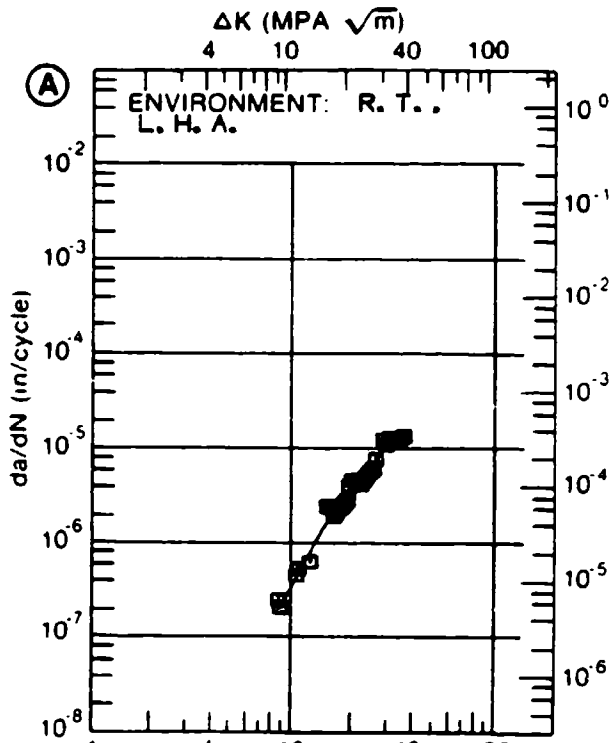


Figure 3.8.3.4

TABLE 3.8.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.5 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E=- 65F L. H. A.			
DELTA K MIN	A: 8.14	.129			
	B:				
	C:				
	D:				
	9.00	.172			
	10.00	.238			
	13.00	.552			
	16.00	1.05			
20.00	2.02				
25.00	3.92				
30.00	7.14				
35.00	12.7				
DELTA K MAX	A: 35.96	14.2			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		6.53			
PERCENT ERROR					

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	
RATIO	0.8-1.25	
SUMMARY	1.25-2.0	1
(NP/NA)	>2.0	

CONDITION/HT: H1000
 FORM: 6.00" TH BILLET
 SPECIMEN TYPE: CT
 ORIENTATION: S-T
 STRESS RATIO: +0.08
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 190.0 KSI
 ULT. STRENGTH: 207.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 4.940"
 REFERENCES: 88579

STAIN.
 STEEL
 PH13-8MO

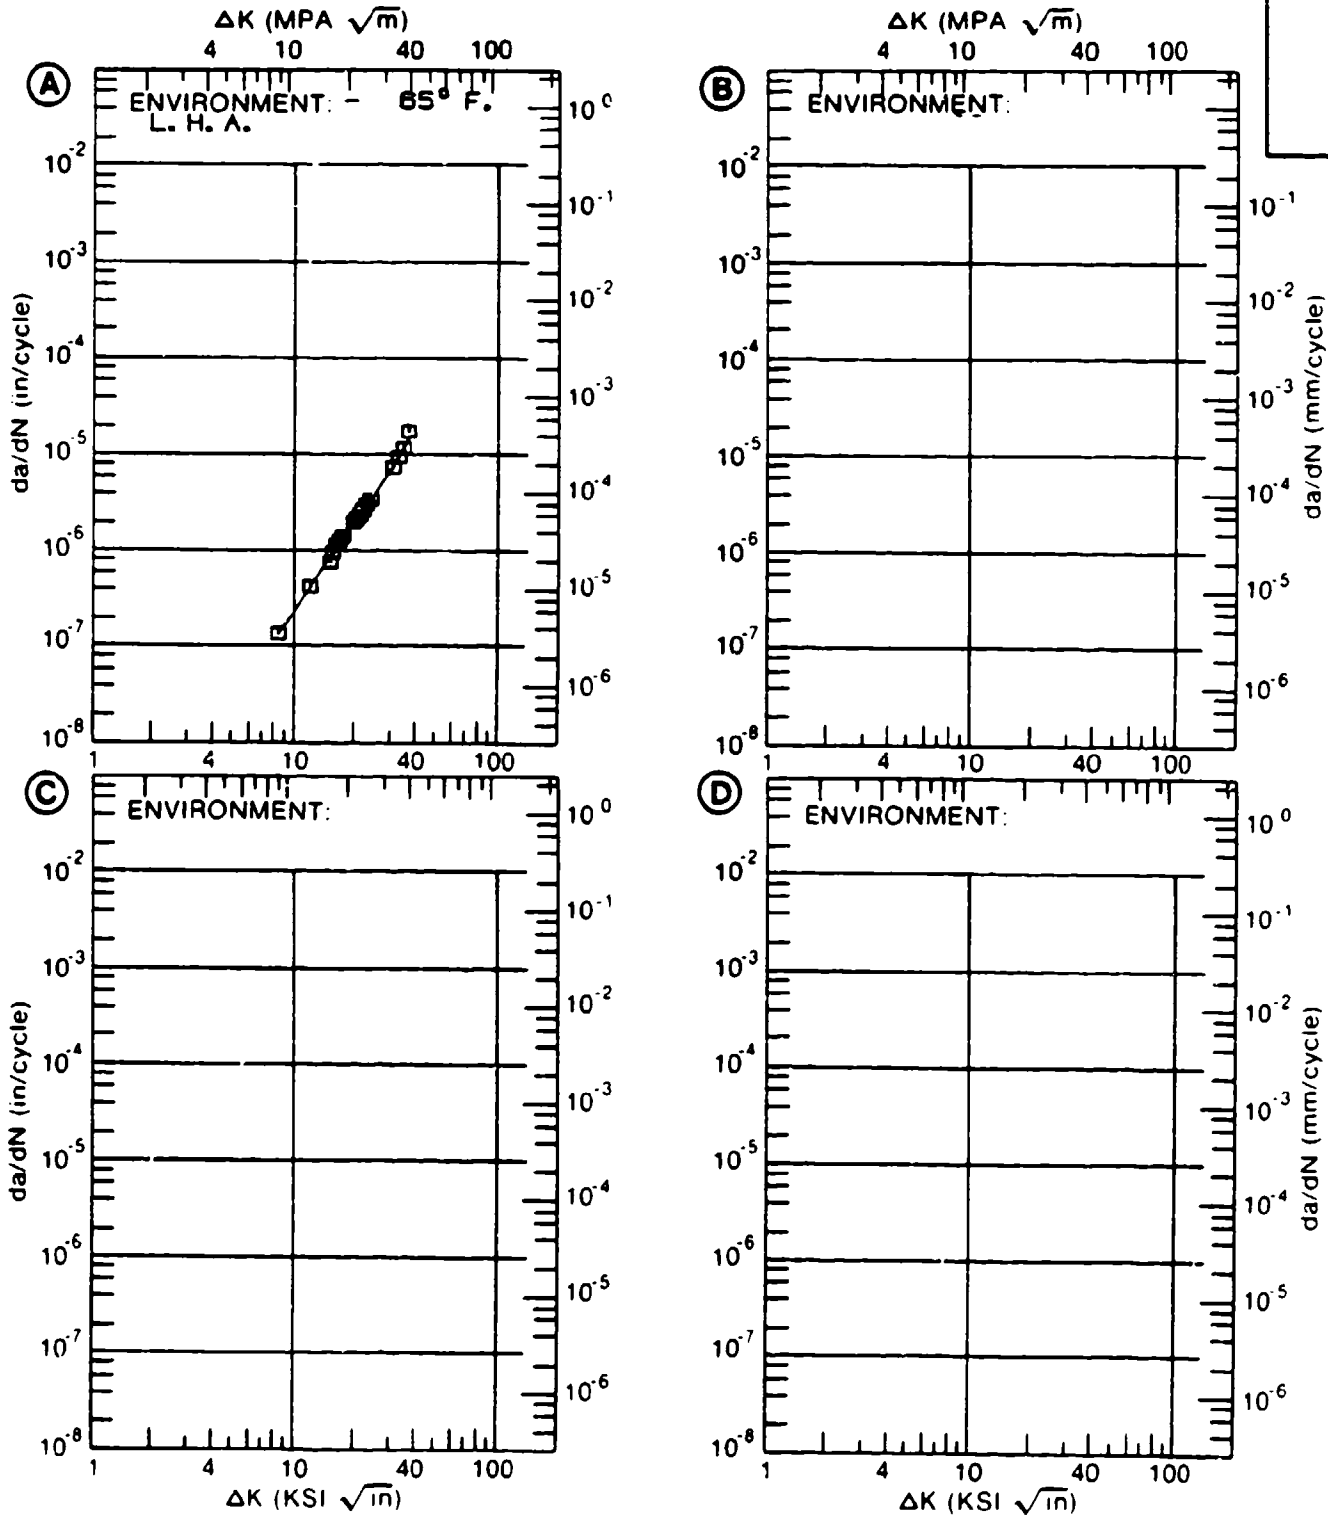


Figure 3.8.3.5

TABLE 3.8.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.6 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000

DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		L. H. A.			
DELTA K MIN	A: 8.63	.241			
	B:				
	C:				
	D:				
	9.00	.256			
	10.00	.340			
	13.00	1.01			
	16.00	2.00			
	20.00	3.47			
	25.00	5.60			
DELTA K MAX	A: 55.15	54.3			
	B:				
	C:				
	D:				
	9.00	.256			
	10.00	.340			
	13.00	1.01			
	16.00	2.00			
	20.00	3.47			
	25.00	5.60			
ROOT MEAN SQUARE		5.25			
PERCENT ERROR					
LIFE	0.0-0.3				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: H1000
 FORM: 22.00" TH BILLET
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 190.0 KSI
 ULT. STRENGTH: 207.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 4.940"
 REFERENCES: 88579

STAIN.
 STEEL
 PH13-8MO

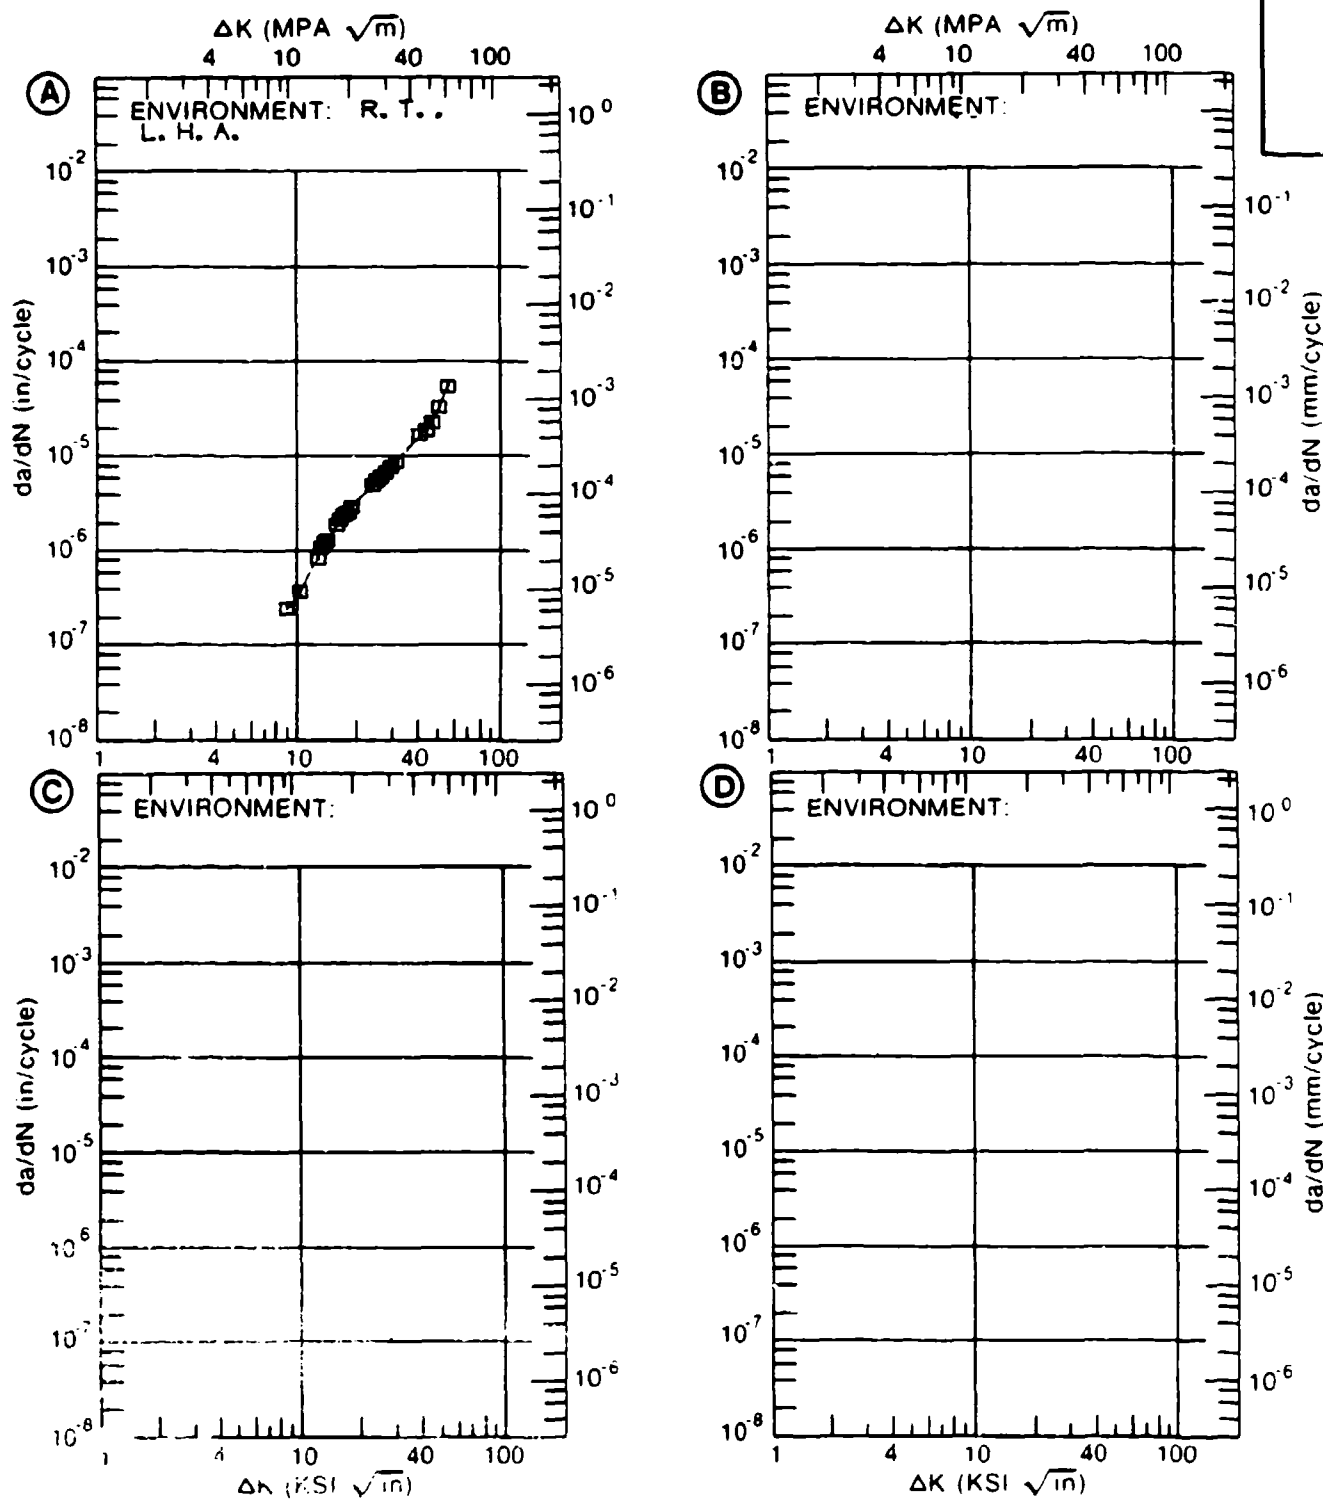


Figure 3.8.3.6

TABLE 3.8.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.7 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000
ENVIRONMENT: R. T., L. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.50		
DELTA K MIN	A: 7.96	.154			
	B: 7.25		.252		
	C:				
	D:				
	8.00	.156	.383		
	9.00	.219	.598		
	10.00	.335	.852		
	13.00	1.12	1.82		
	16.00	2.31	3.10		
	20.00	3.83	5.59		
25.00	5.93	11.0			
30.00	9.36	21.3			
35.00	15.7				
40.00	24.2				
50.00	34.1				
DELTA K MAX	A: 59.52	48.3			
	B: 33.12		32.5		
	C:				
	D:				

APPROXIMATE RANGE 15.95 11.43

REVISION 0-0-0
PREDICTION 0-0-0
RATIO 1-1.25 2 2
SUMMARY 5-2.0 1
APPROXIMATE 2.0

CONDITION/HT: H1000
 FORM: 1.50" TH EXTRUDED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.0 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 214.0 KSI
 ULT. STRENGTH: 221.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 6.170- 6.180"
 REFERENCES: 88579

STAIN.
 STEEL
 PH13-8MO

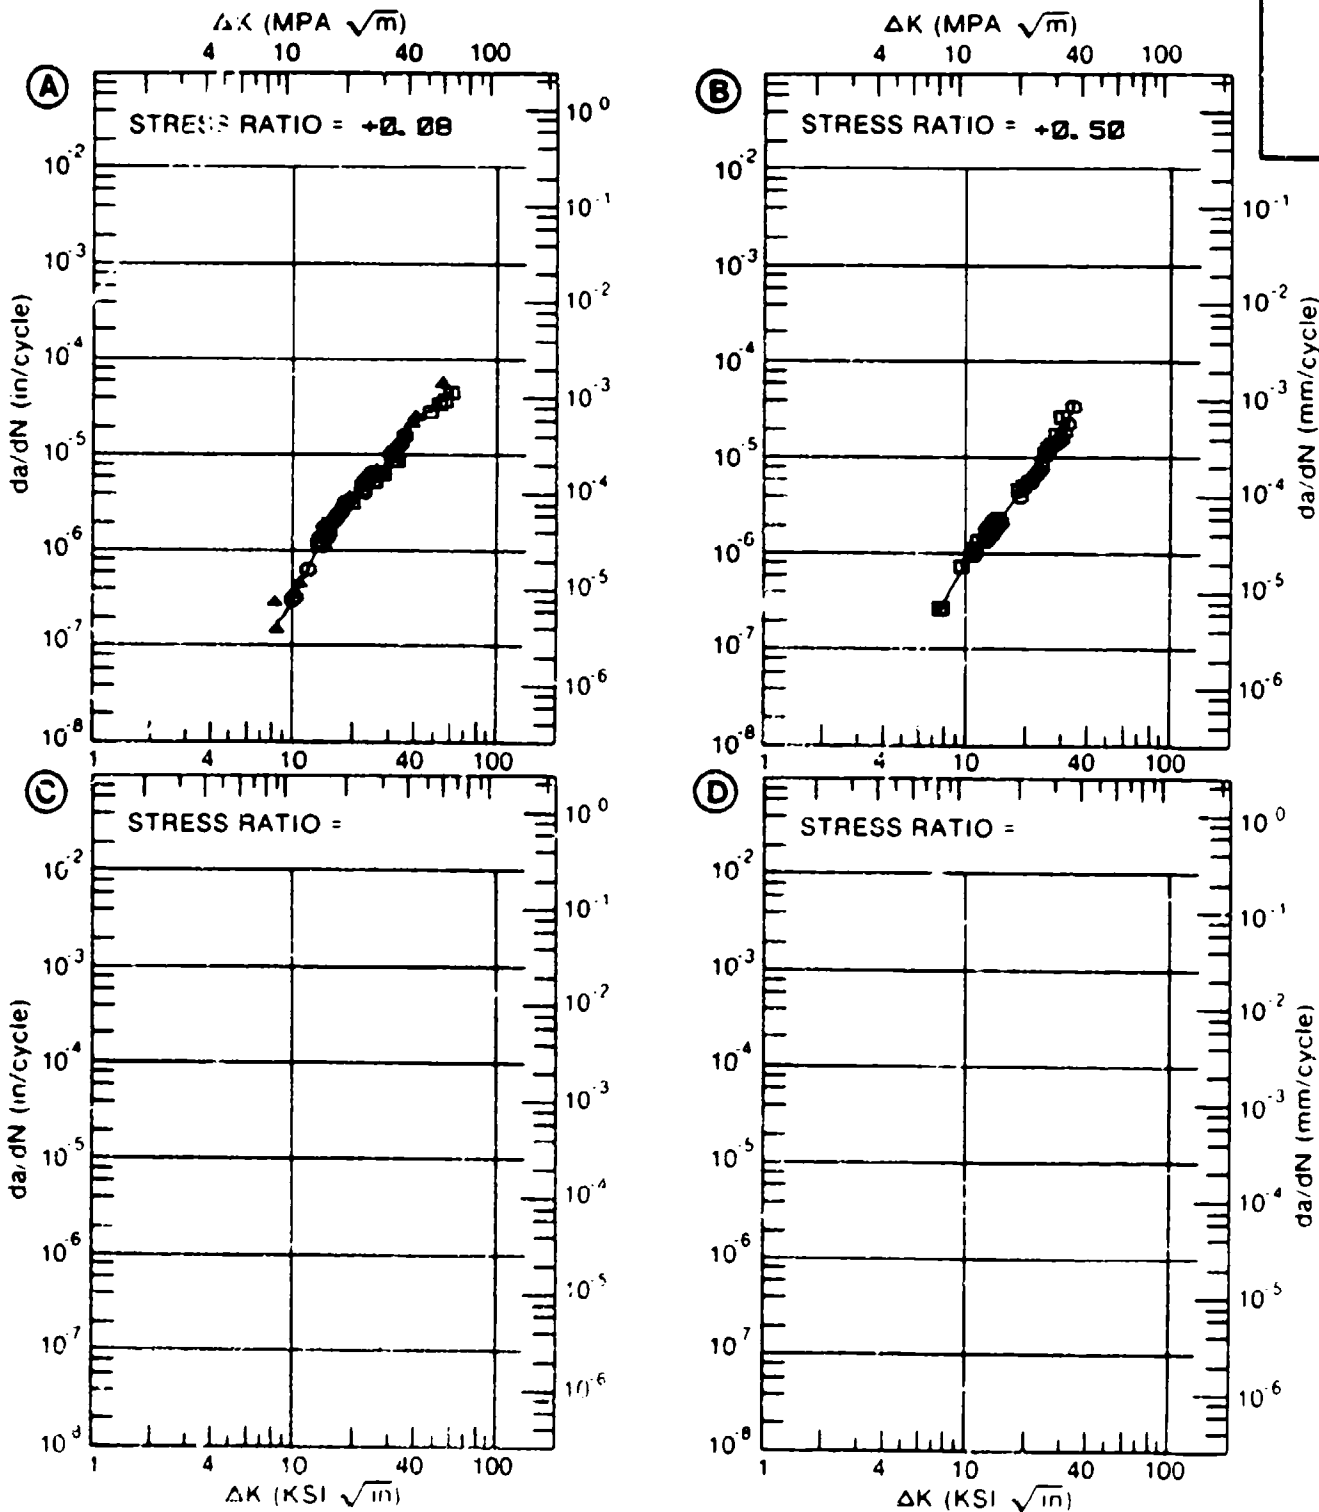


Figure 3.8.3.7

TABLE 3.8.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.8 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. L. H. A. -6. OHZ	E=- 65 F L. H. A. -6. OHZ	E= R. T. S. T. W. -1. OHZ	
MIN	A: 7.96	.156	.112	.388	
	B: 7.62				
	C: 8.27				
	D:				
	8.00	.157	.123		
	9.00	.216	.167	.479	
	10.00	.331	.236	.643	
	13.00	1.14	.635	1.49	
	16.00	2.33	1.31	3.13	
	20.00	3.73	2.87	7.11	
	25.00	5.82	4.64	15.8	
	30.00	9.82		29.0	
	35.00	16.2			
	40.00	23.2			
	50.00	34.4			
MAX	A: 59.52	46.5	12.3	43.7	
	B: 29.92				
	C: 34.43				
	D:				
ROOT MEAN SQUARE		16.24	16.25	8.27	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25	2	1	1	
	1.25-2.0	1			
	2.0				

CONDITION/HT: H1000
 FORM: 1.50" TH EXTRUDED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 208.0- 214.0 KSI
 ULT. STRENGTH: 216.0- 221.0 KSI
 SPECIMEN THK: 0.999- 1.000"
 SPECIMEN WIDTH: 6.170- 6.180"
 REFERENCES: 88579, 85837

STAIN.
 STEEL

PH13-8MO

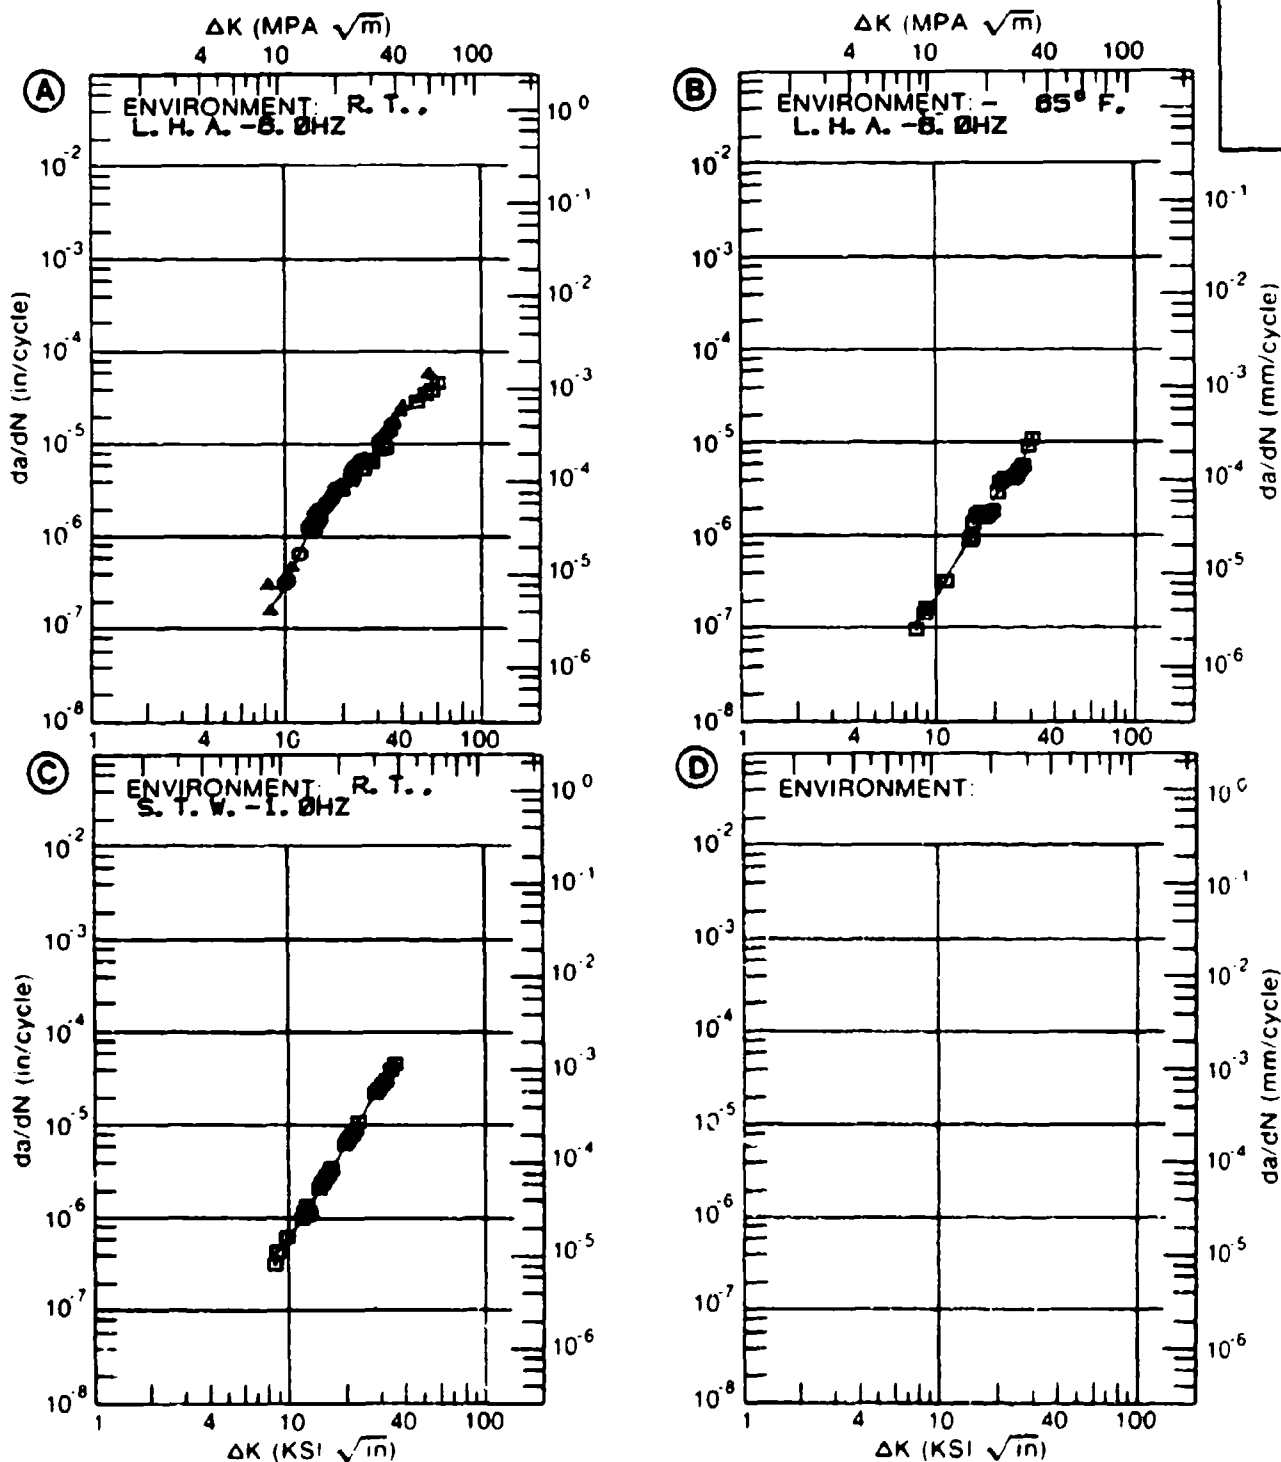


Figure 3.9.3.8

TABLE 3.8.3.9

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.9 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E= R. T. SIM. SEA WATER		
DELTA K	A: 12.29	1.26			
MIN	B: 12.13		1.30		
	C:				
	D:				
	13.00	1.53	1.82		
	16.00	2.99	4.36		
	20.00	5.44	9.07		
	25.00	9.04	16.1		
	30.00	13.0	23.9		
	35.00	17.3	32.3		
	40.00	21.8	41.8		
	50.00	31.9	65.5		
	60.00	44.0	99.7		
	70.00	58.6			
	80.00	76.7			
	90.00	99.1			
	100.00	127.			
	130.00	259.			
DELTA K	A: 154.80	457.			
MAX	B: 69.01		145.		
	C:				
	D:				

ROOT MEAN SQUARE 6.33 11.04
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2 2
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: H1000
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 1.00- 10.00 HZ

YIELD STRENGTH: 205.0 KSI
 ULT. STRENGTH: 210.6 KSI
 SPECIMEN THK: 1.003- 1.005"
 SPECIMEN WIDTH: 4.500- 7.400"
 REFERENCES: NC002

STAIN.
 STEEL

PH13-8MO

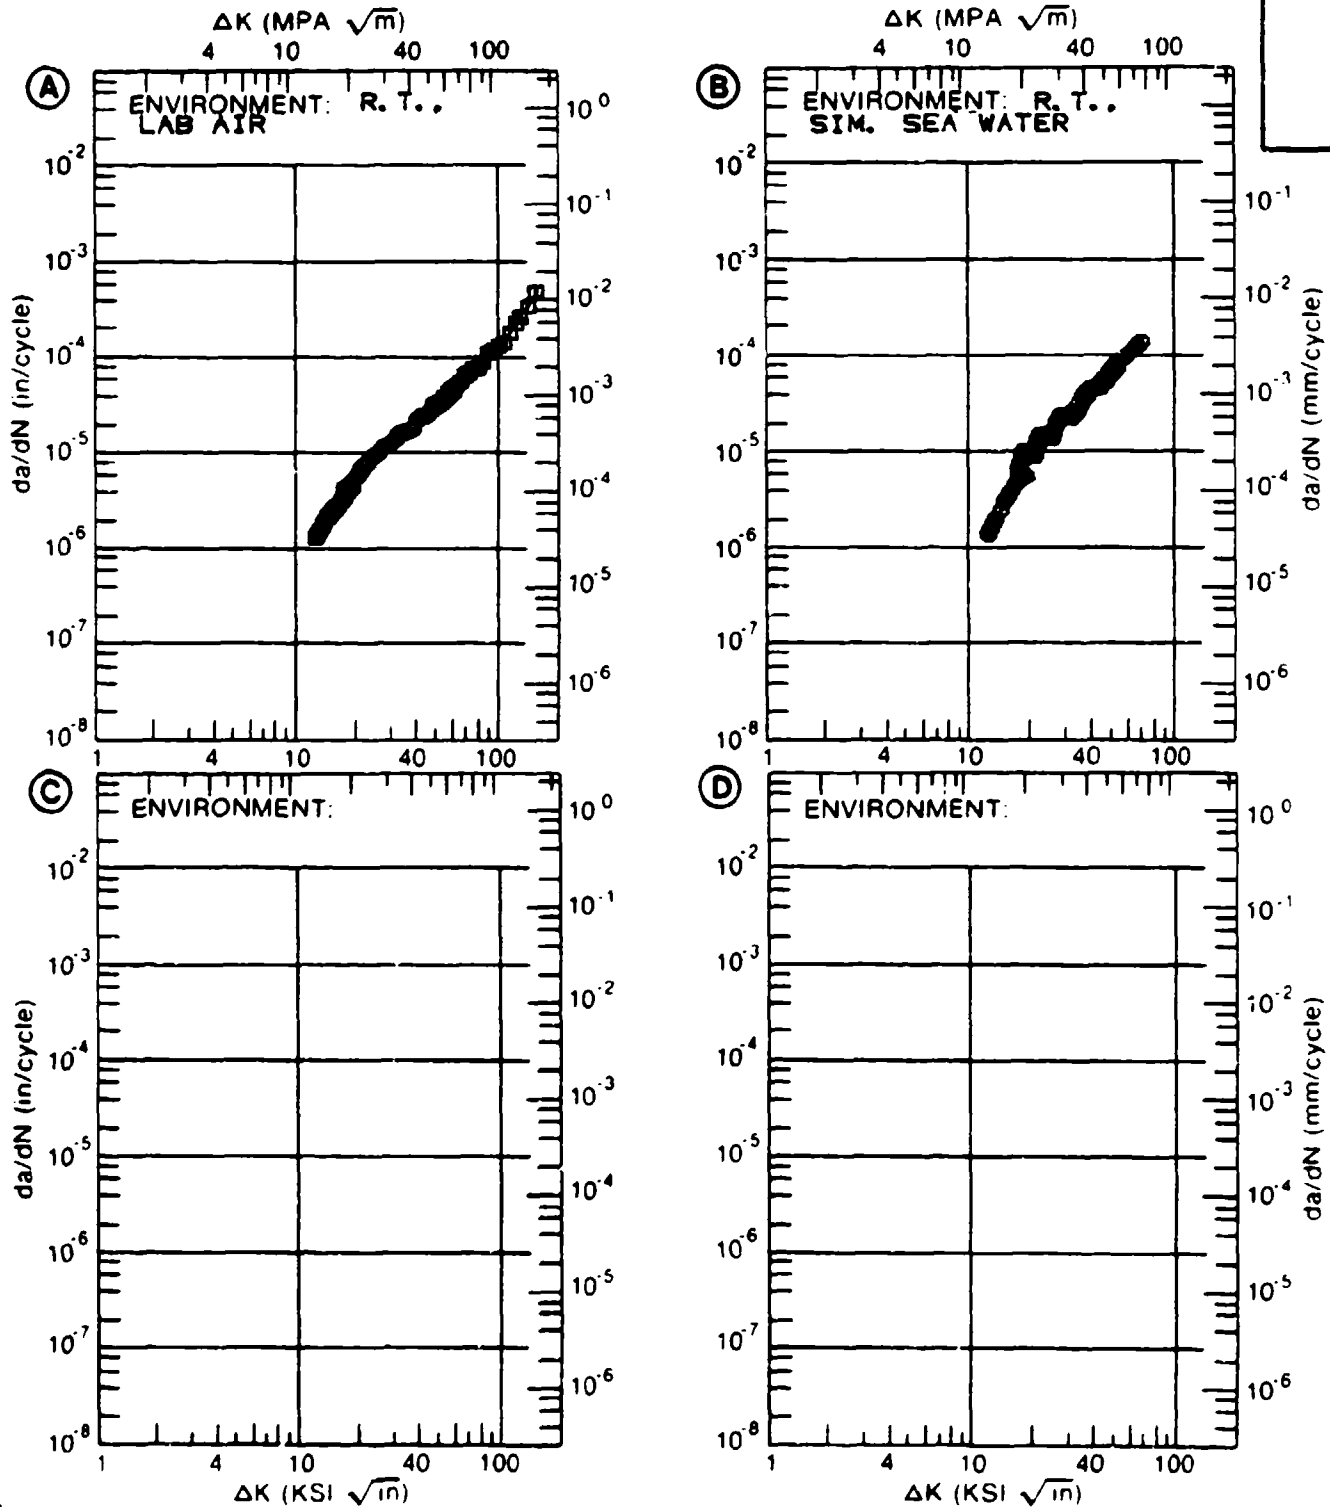


Figure 3.8.3.9

TABLE 3.8.3.10

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.10 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E= R. T. SIM. SEA WATER		
DELTA K	A: 12.18	1.37			
MIN	B: 12.34		1.57		
	C:				
	D:				
	13.00	1.70	1.93		
	16.00	3.16	4.42		
	20.00	5.57	8.95		
	25.00	9.04	15.5		
	30.00	12.9	22.8		
	35.00	17.0	31.2		
	40.00	21.6	40.9		
	50.00	32.1	65.4		
	60.00	45.2	99.7		
	70.00	61.7	148.		
	80.00	82.8	212.		
	90.00	110.	296.		
	100.00	145.	404.		
	130.00		896.		
DELTA K	A: 116.68	226.			
MAX	B: 137.87		1074.		
	C:				
	D:				

ROOT MEAN SQUARE 6.87 12.77
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2 2
SUMMARY 1.25-2.0
(NP/NA) 2.0

CONDITION/HT: H1000
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 1.00- 10.00 HZ

YIELD STRENGTH: 205.4 KSI
 ULT. STRENGTH: 210.0 KSI
 SPECIMEN THK: 1.003- 1.005"
 SPECIMEN WIDTH: 4.500- 7.400"
 REFERENCES: NC002

STAIN.
 STEEL

PH13-8MO

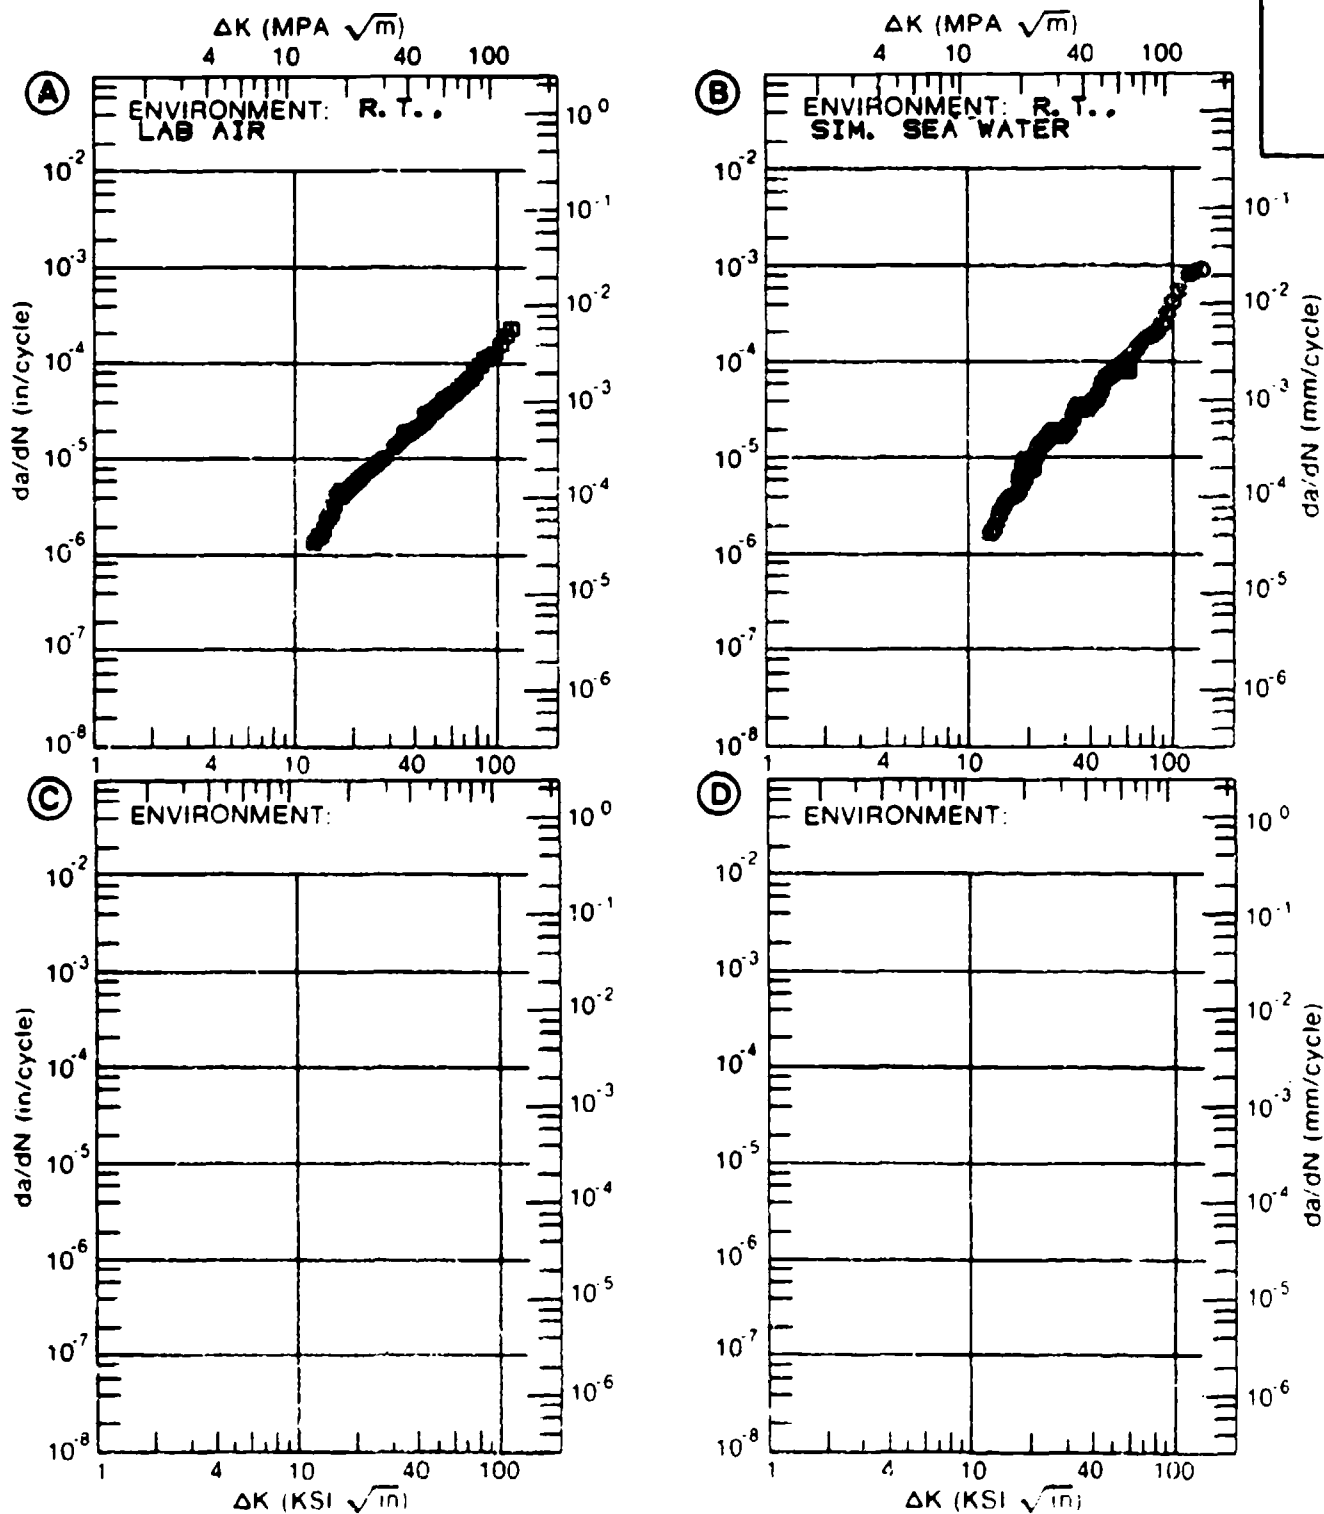


Figure 3.8.3.10

TABLE 3.8.3.11

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.11 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000
ENVIRONMENT: F. T. , DRY AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 30	R=+0. 50	
DELTA K	A: 8. 91	. 137			
MIN	B: 7. 44		. 177		
	C: 6. 27			. 0264	
	D:				
	7. 00			. 120	
	8. 00		. 244	. 243	
	9. 00	. 144	. 393	. 413	
	10. 00	. 239	. 582	. 641	
	13. 00	. 724	1. 36	1. 58	
	16. 00	1. 53	2. 41	2. 80	
	20. 00	3. 07	4. 17	4. 79	
	25. 00	5. 69	6. 96	8. 03	
	30. 00	9. 00	10. 5	12. 6	
	35. 00	13. 0	15. 1	19. 5	
	40. 00	17. 7	21. 1		
	50. 00	29. 6			
	60. 00	45. 7			
	70. 00	67. 2			
	80. 00	95. 9			
DELTA K	A: 85. 01	114.			
MAX	B: 40. 86		22. 2		
	C: 37. 95			25. 1	
	D:				
ROOT MEAN SQUARE		5. 19	5. 60	6. 49	
PERCENT ERROR					
LIFE	0 0-0 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25	1	1	1	
SUMMARY	1. 25-2. 0				
(NP/NA)	22 0				

CONDITION/HT: H1000
 FORM: 1.00" TH FORGED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 8.0 HZ
 ENVIRONMENT: R. T., DRY AIR

YIELD STRENGTH: 215.0 KSI
 ULT. STRENGTH: 221.0 KSI
 SPECIMEN THK: 0.500- 0.502"
 SPECIMEN WIDTH: 3.987- 3.992"
 REFERENCES: GD009

STAIN.
 STEEL
 PH13-8MO

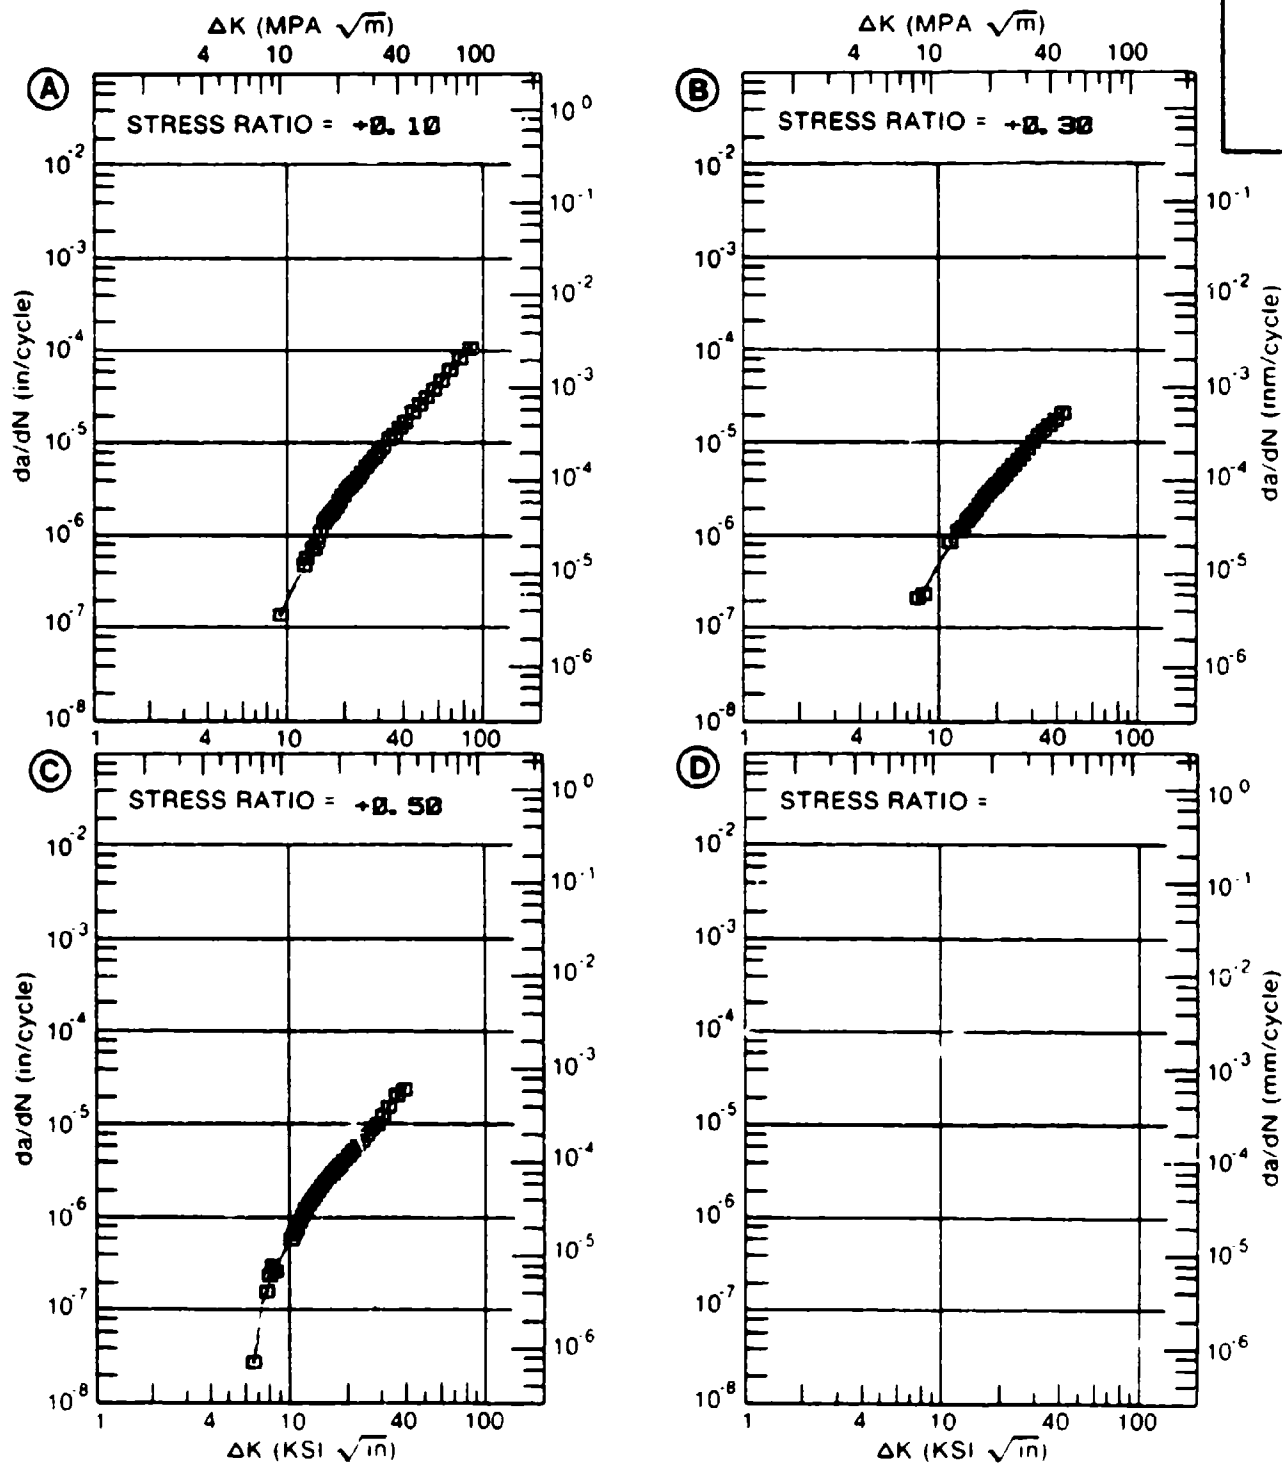


Figure 3.8.3.11

TABLE 3.8.3.12

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.12 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000
ENVIRONMENT: R. T., H. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.30	R=+0.50	
DELTA K	A: 9.78	.219			
MIN	B: 9.28		.576		
	C: 6.78			.393	
	D:				
	7.00			.299	
	8.00			.375	
	9.00			.592	
	10.00	.294	.218	.942	
	13.00	1.52	2.50	2.89	
	16.00	3.61	5.41	6.11	
	20.00	7.56	11.3	12.5	
	25.00	16.0	21.9	24.6	
	30.00	28.7	36.0	43.1	
	35.00	45.4	53.6	71.2	
	40.00	64.9	74.8	114.	
	50.00	105.	129.		
DELTA K	A: 59.32	133.			
MAX	B: 50.68		134.		
	C: 47.33			221.	
	D:				
ROOT MEAN SQUARE		13.22	7.15	11.69	
PERCENT ERROR					

LIFE	0.0-0.5			
PREDICTION	0.5-0.8			
RATIO	0.8-1.25	2	2	2
SUMMARY	1.25-2.0			
(NP/NA)	>2.0			

CONDITION/HT: H1000
 FORM: 1.00" TH FORGED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.0 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 215.0 KSI
 ULT. STRENGTH: 221.0 KSI
 SPECIMEN THK: 0.501 - 0.504"
 SPECIMEN WIDTH: 3.986 - 4.006"
 REFERENCES: GD009

STAIN.
 STEEL
 PH13-8MO

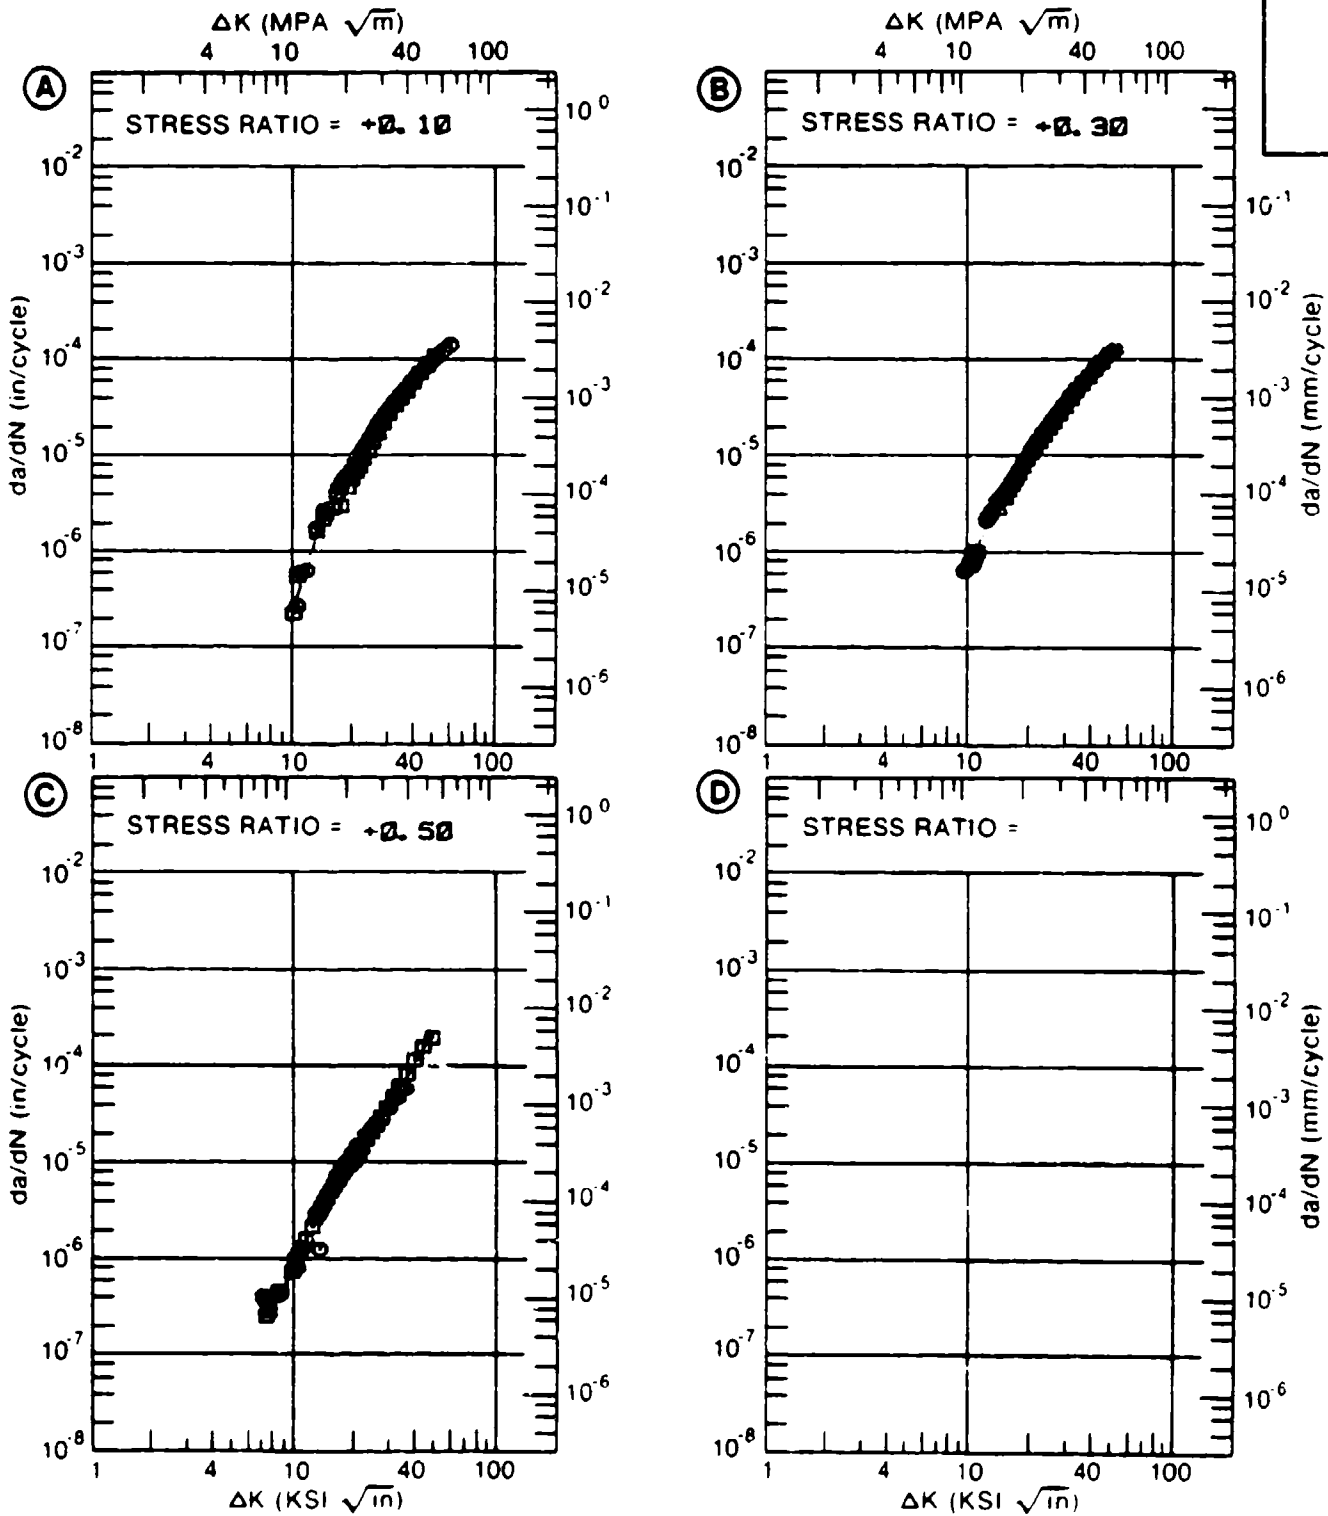


Figure 3.8.3.12

TABLE 3.8.3.13

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.13 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000
ENVIRONMENT: R.T., DRY AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.30	R=+0.50	
DELTA K MIN	A: 9.25	.147			
	B: 7.78		.176		
	C: 6.00			.121	
	D:				
	7.00			.153	
	8.00		.193	.220	
	9.00		.289	.335	
	10.00	.265	.426	.511	
	13.00	.737	1.15	1.40	
	16.00	1.59	2.29	2.62	
	20.00	3.14	4.17	4.60	
	25.00	5.52	6.93	7.62	
	30.00	8.27	10.2	11.5	
	35.00	11.4	14.4	16.8	
	40.00	15.0	19.8	24.1	
	50.00	24.3	37.1		
60.00	37.7	69.9			
70.00	57.6	134.			
80.00	87.4				
DELTA K MAX	A: 86.50	116.			
	B: 73.72		171.		
	C: 48.04			42.9	
	D:				

ROOT MEAN SQUARE PERCENT ERROR 8.22 7.37 6.14

LIFE 0.0-0.5
PREDICTION 0.5-0.8
FATIG 0.8-1.25 1 1
SUMMARY 1.25-2.0 1
(NF/NA) 1.2.0

CONDITION/HT: H1000
 FORM: 1.00" TH FORGED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 6.0 HZ
 ENVIRONMENT: R. T., DRY AIR

YIELD STRENGTH: 216.0 KSI
 ULT. STRENGTH: 222.6 KSI
 SPECIMEN THK: 0.502- 0.503"
 SPECIMEN WIDTH: 3.991- 3.993"
 REFERENCES: GD009

STAIN.
 STEEL
 PH13-8MO

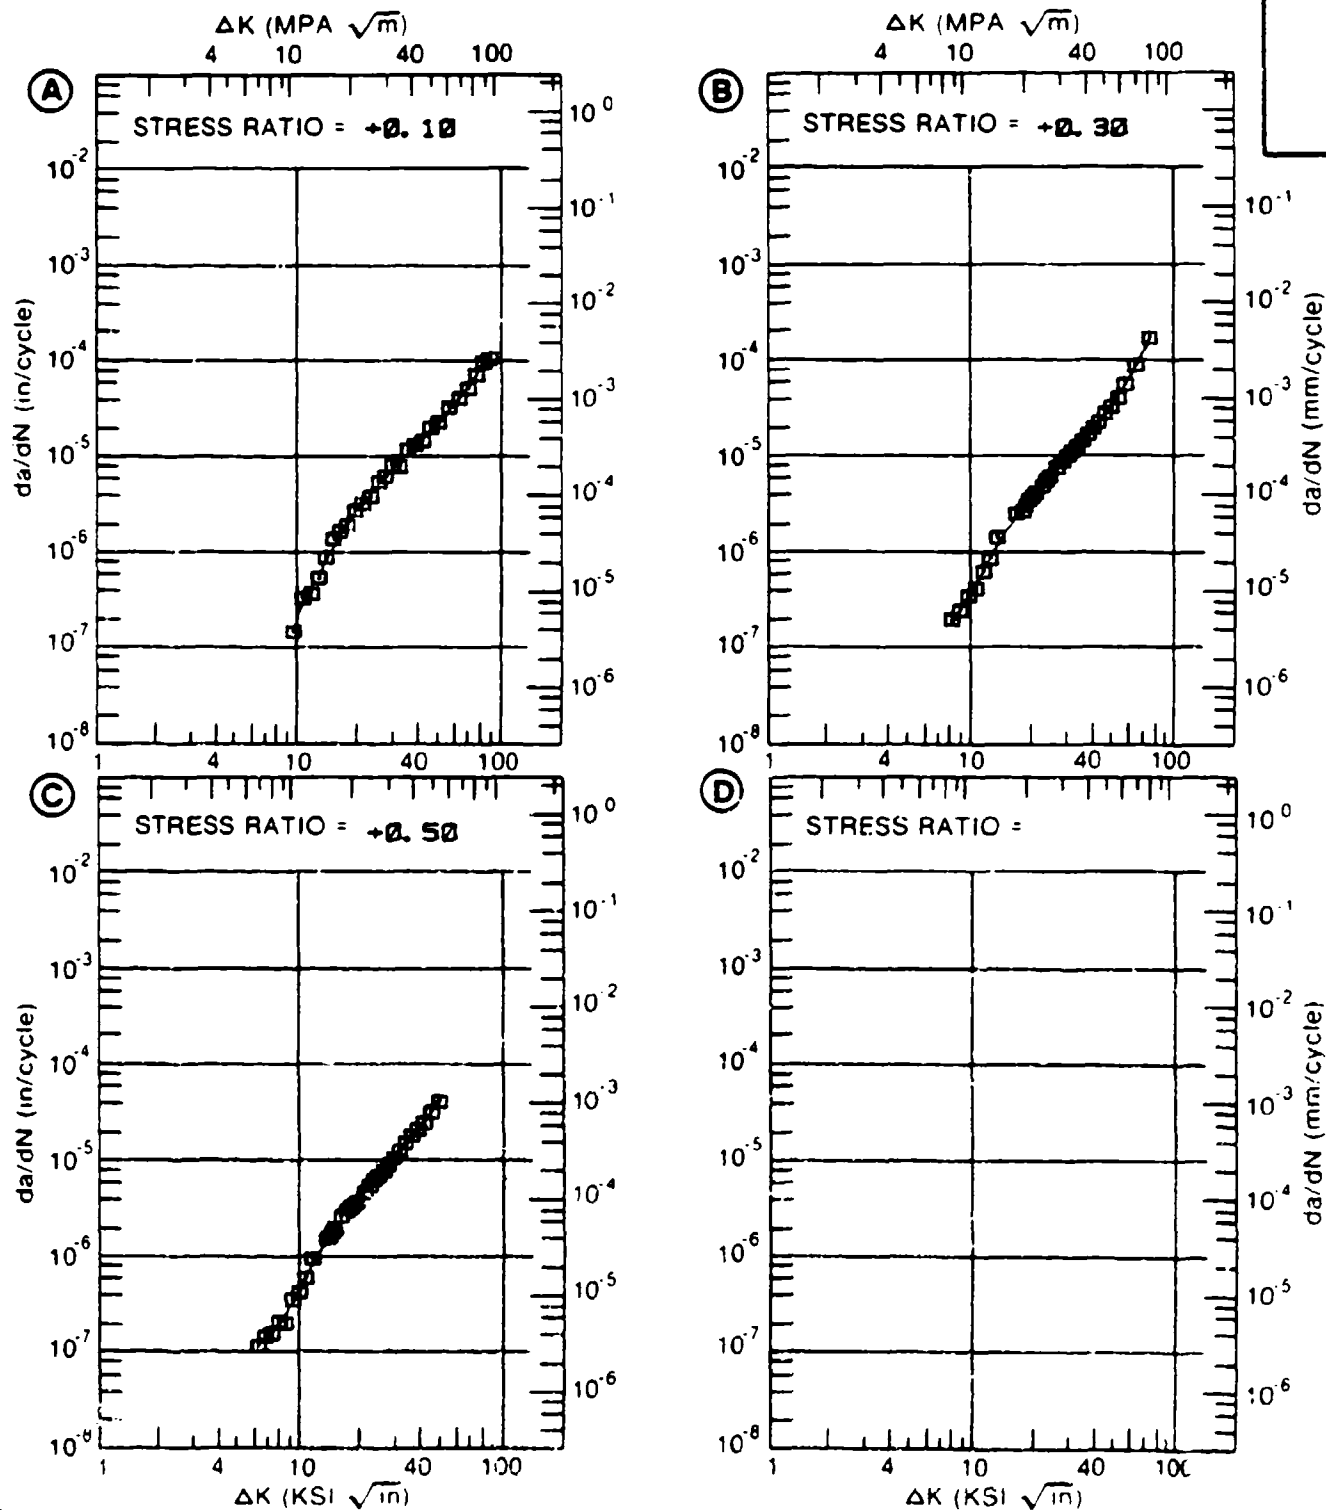


Figure 3.8.3.13

TABLE 3.8.3.14

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.14 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000
ENVIRONMENT: R. T., H. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.30	R=+0.50	
DELTA K	A: 11.42	.928			
MIN	B: 9.13		.466		
	C: 6.87			.299	
	D:				
	7.00			.342	
	8.00			.468	
	9.00			.625	
	10.00		.543	1.08	
	13.00	1.09	2.16	3.06	
	16.00	2.57	4.48	5.84	
	20.00	6.71	9.37	11.6	
	25.00	15.3	19.2	24.3	
	30.00	26.6	34.6	47.9	
	35.00	38.7	58.0	91.9	
	40.00	52.4	92.8	174.	
	50.00	108.	215.	607.	
	60.00	259.			
DELTA K	A: 62.14	303.			
MAX	B: 56.12		339.		
	C: 50.46			613.	
	D:				
ROOT MEAN SQUARE		33.16	14.35	12.25	
PERCENT ERROR					

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO / 0.8-1.25 2
SUMMARY 1.25-2.0 1
(NP/NA) 2.0

CONDITION/HT: H1000
 FORM: 1.00" TH FORGED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 1.0 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 216.0 KSI
 ULT STRENGTH: 222.0 KSI
 SPECIMEN THK: 0.489 - 0.504"
 SPECIMEN WIDTH: 3.982 - 4.117"
 REFERENCES: GD009

STAIN.
 STEEL

PH13-8MO

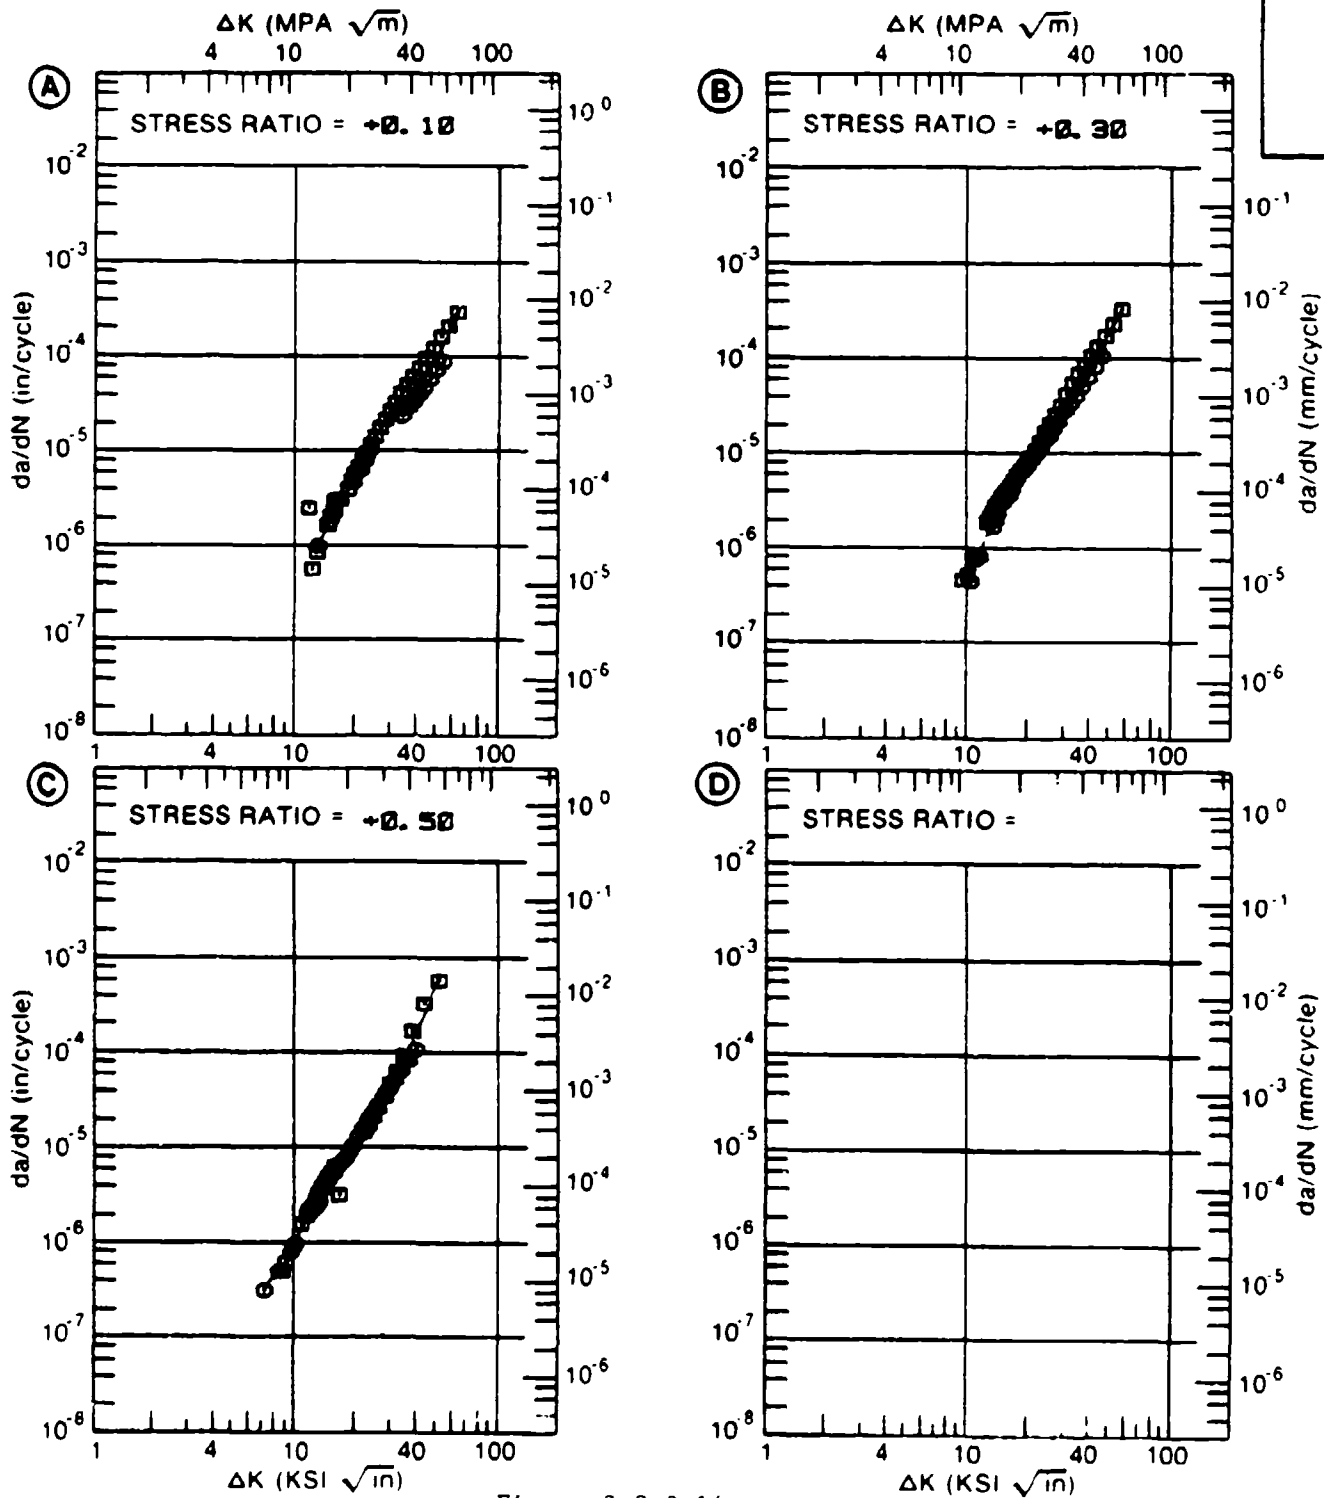


Figure 3.8.3.14

TABLE 3.8.3.15

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 3.8.3.15 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL PH13-8MO
 CONDITION: H1000
 ENVIRONMENT: R. T., L. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	R=+0.08	R=+0.30	R=+0.50	
A: 10.78	.447			
DELTA K B: 10.25		.571		
MIN C: 6.81			.119	
D:				
7.00			.132	
8.00			.220	
9.00			.345	
10.00			.515	
13.00	1.52	1.29	1.33	
16.00	3.49	2.52	2.60	
20.00	5.82	4.70	4.70	
25.00	8.52	8.11	7.10	
30.00	12.7	13.4		
A: 34.32	19.9			
DELTA K B: 34.71		18.7		
MAX C: 29.25			8.31	
D:				
ROOT MEAN SQUARE	10.57	17.34	9.04	
PERCENT ERROR				

LIFE	0.0-0.5			
PREDICTION	0.5-0.8			
RATIO	0.8-1.25	1	1	1
SUMMARY	1.25-2.0			
(NP/NA)	>2.0			

CONDITION/HT: H1000
 FORM: 4.00" TH FORGED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.0 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 201.0 KSI
 ULT. STRENGTH: 212.0 KSI
 SPECIMEN THK: 0.990- 0.998"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 85837, 88578

STAIN.
 STEEL

PH13-8MO

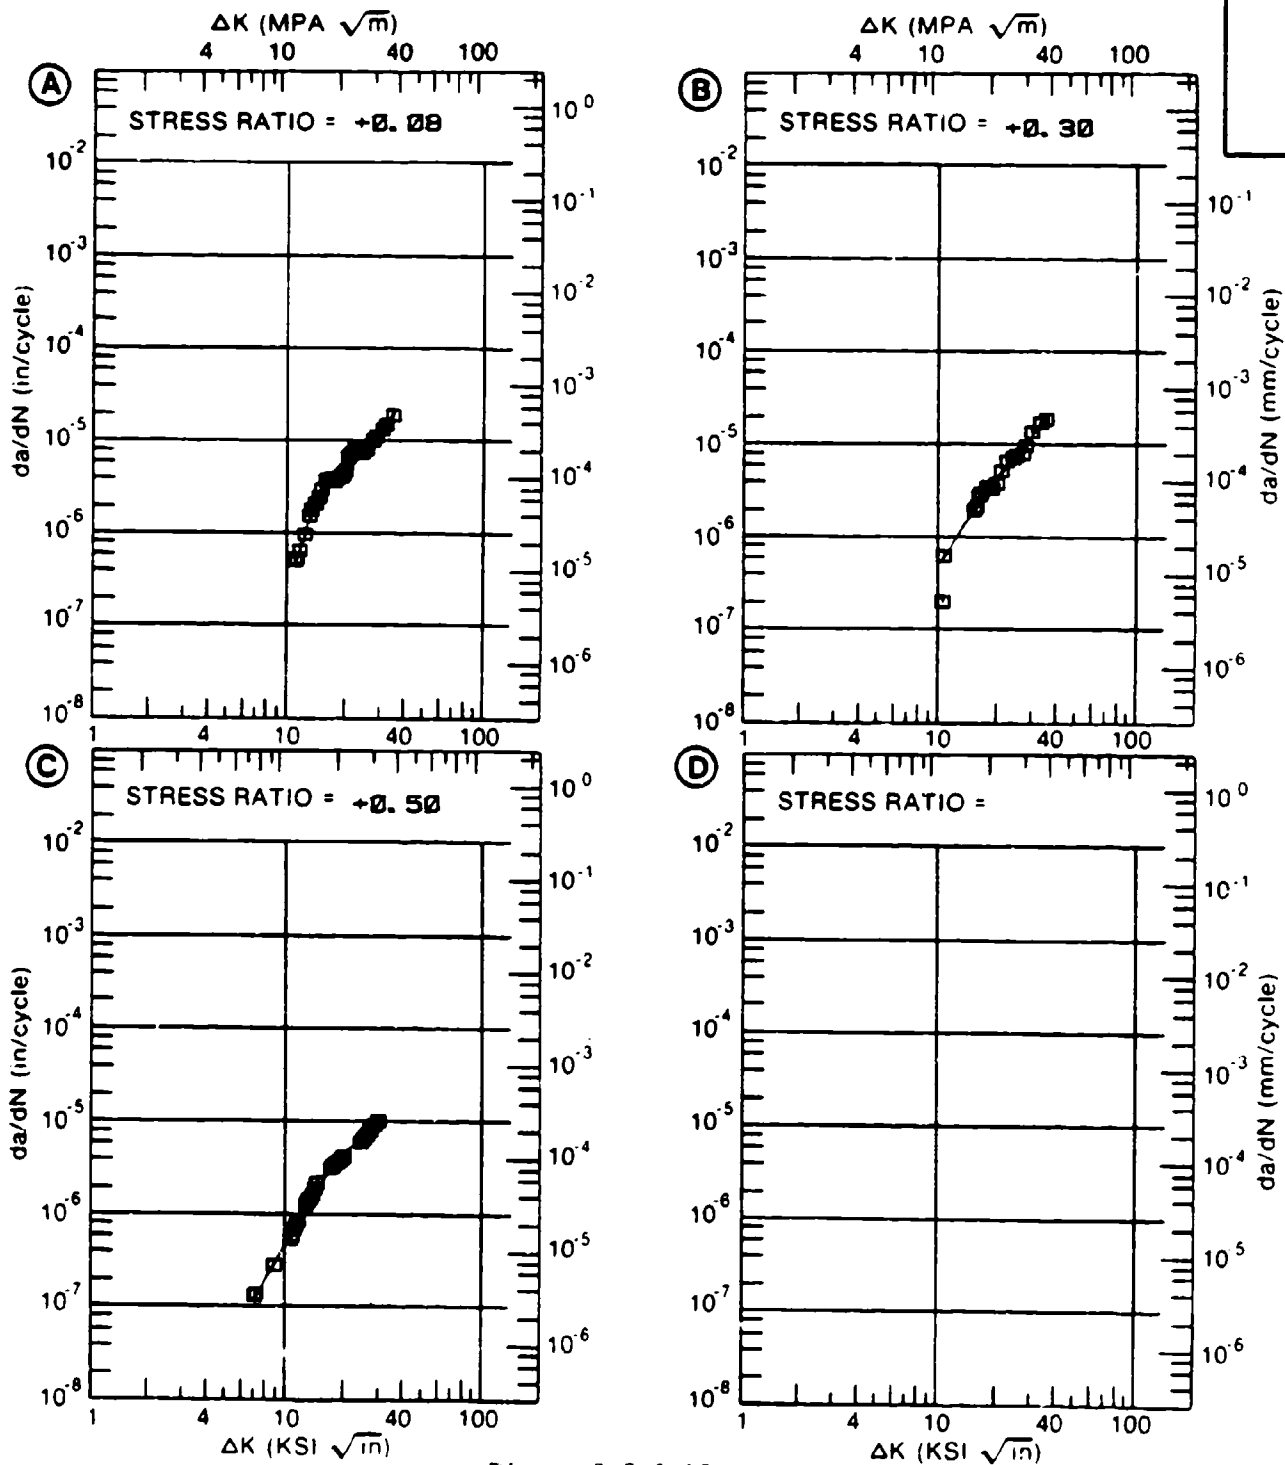


Figure 3.8.3.15

TABLE 3.8.3.16

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.16 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL PH13-BMO
CONDITION: H1000

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. I. S. T. W.			
DELTA K MIN	A: 10.68	1.11			
	B:				
	C:				
	D:				
	13.00	2.92			
	16.00	7.61			
DELTA K MAX	20.00	18.5			
	25.00	36.1			
	30.00	50.1			
	A: 33.64	54.6			
	B:				
	C:				
D:					

ROOT MEAN SQUARE 8.98
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: H1000
 FORM: 4.00" TH FORGED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 1.0 HZ

YIELD STRENGTH: 198.0 KSI
 ULT. STRENGTH: 206.0 KSI
 SPECIMEN THK: 0.991"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 05837

STAIN.
 STEEL
 PH13-8MO

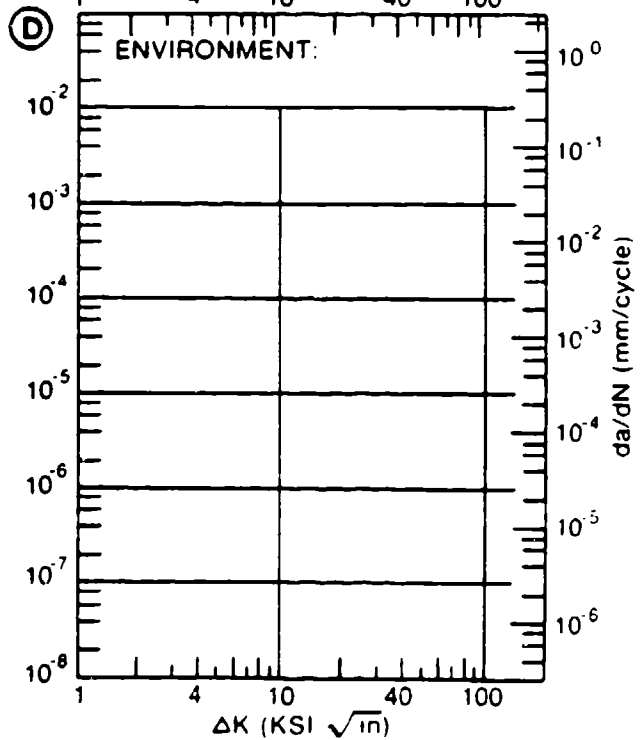
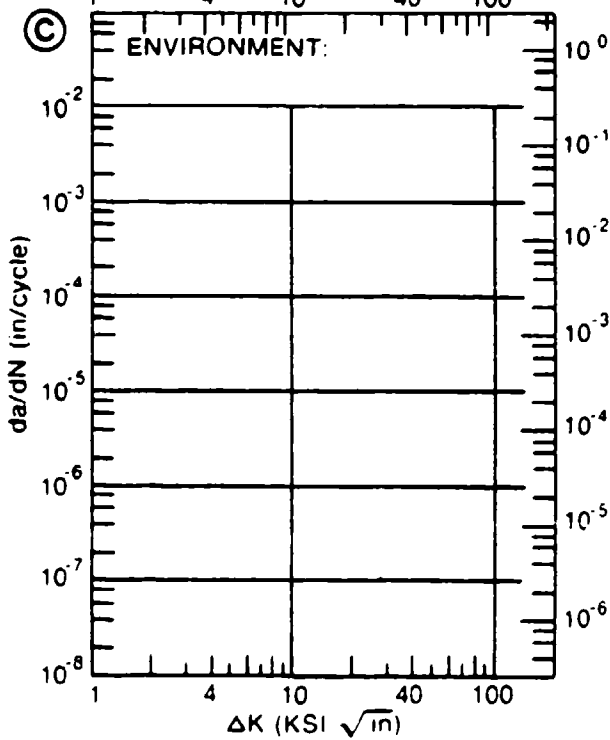
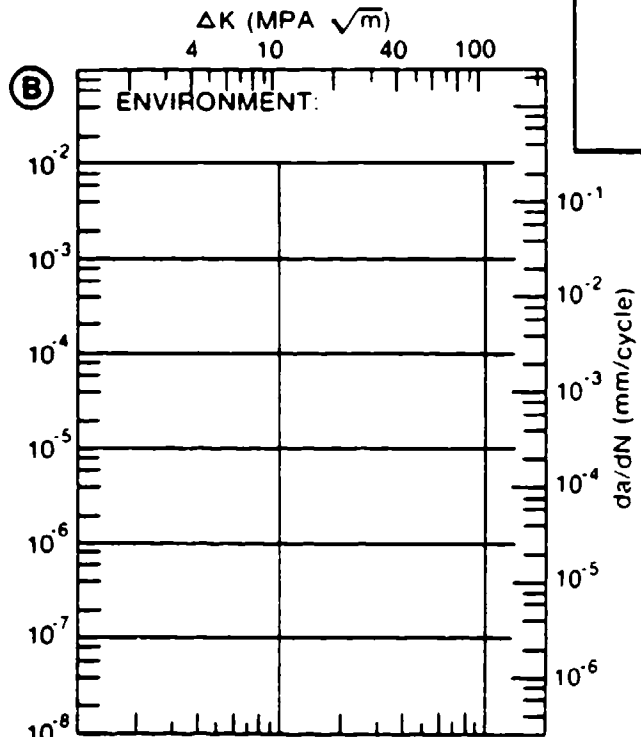
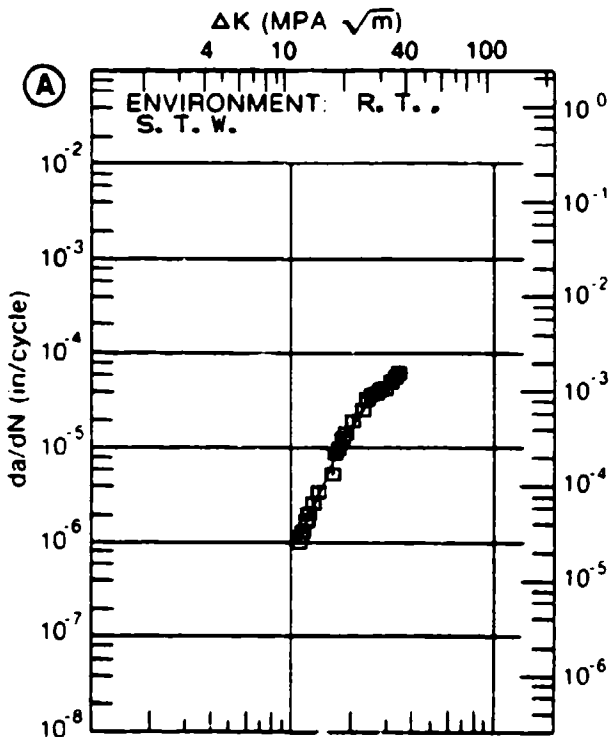


Figure 3.8.3.16

TABLE 3.8.3.17

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.17 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: STAINLESS STEEL PH13-BMO

CONDITION: H1000

ENVIRONMENT: R.T., L.H.A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30	R=+0.50	
DELTA K MIN	A: 8.33	.155			
	B: 9.50		.514		
	C: 9.52			.593	
	D:				
	9.00	.194			
	10.00	.290	.624	.792	
	13.00	.931	1.49	2.02	
	16.00	1.92	2.61	3.20	
	20.00	3.40	4.39	5.09	
	25.00	5.43	7.05	7.90	
	30.00	7.97	10.3	11.7	
	35.00	12.1	14.4	19.4	
	40.00	19.4	19.7	38.0	
DELTA K MAX	A: 42.46	15.5			
	B: 42.47		22.8		
	C: 41.04			44.6	
	D:				
ROOT MEAN SQUARE		12.32	5.40	7.95	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	2	1	1	

CONDITION/HT: H1000
 FORM: 1.50" TH ROLLED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.0 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 200.0 KSI
 ULT. STRENGTH: 216.0 KSI
 SPECIMEN THK: 0.251 - 0.990"
 SPECIMEN WIDTH: 7.390 - 7.400"
 REFERENCES: 80579, 85837

STAIN.
 STEEL
 PH13-8MO

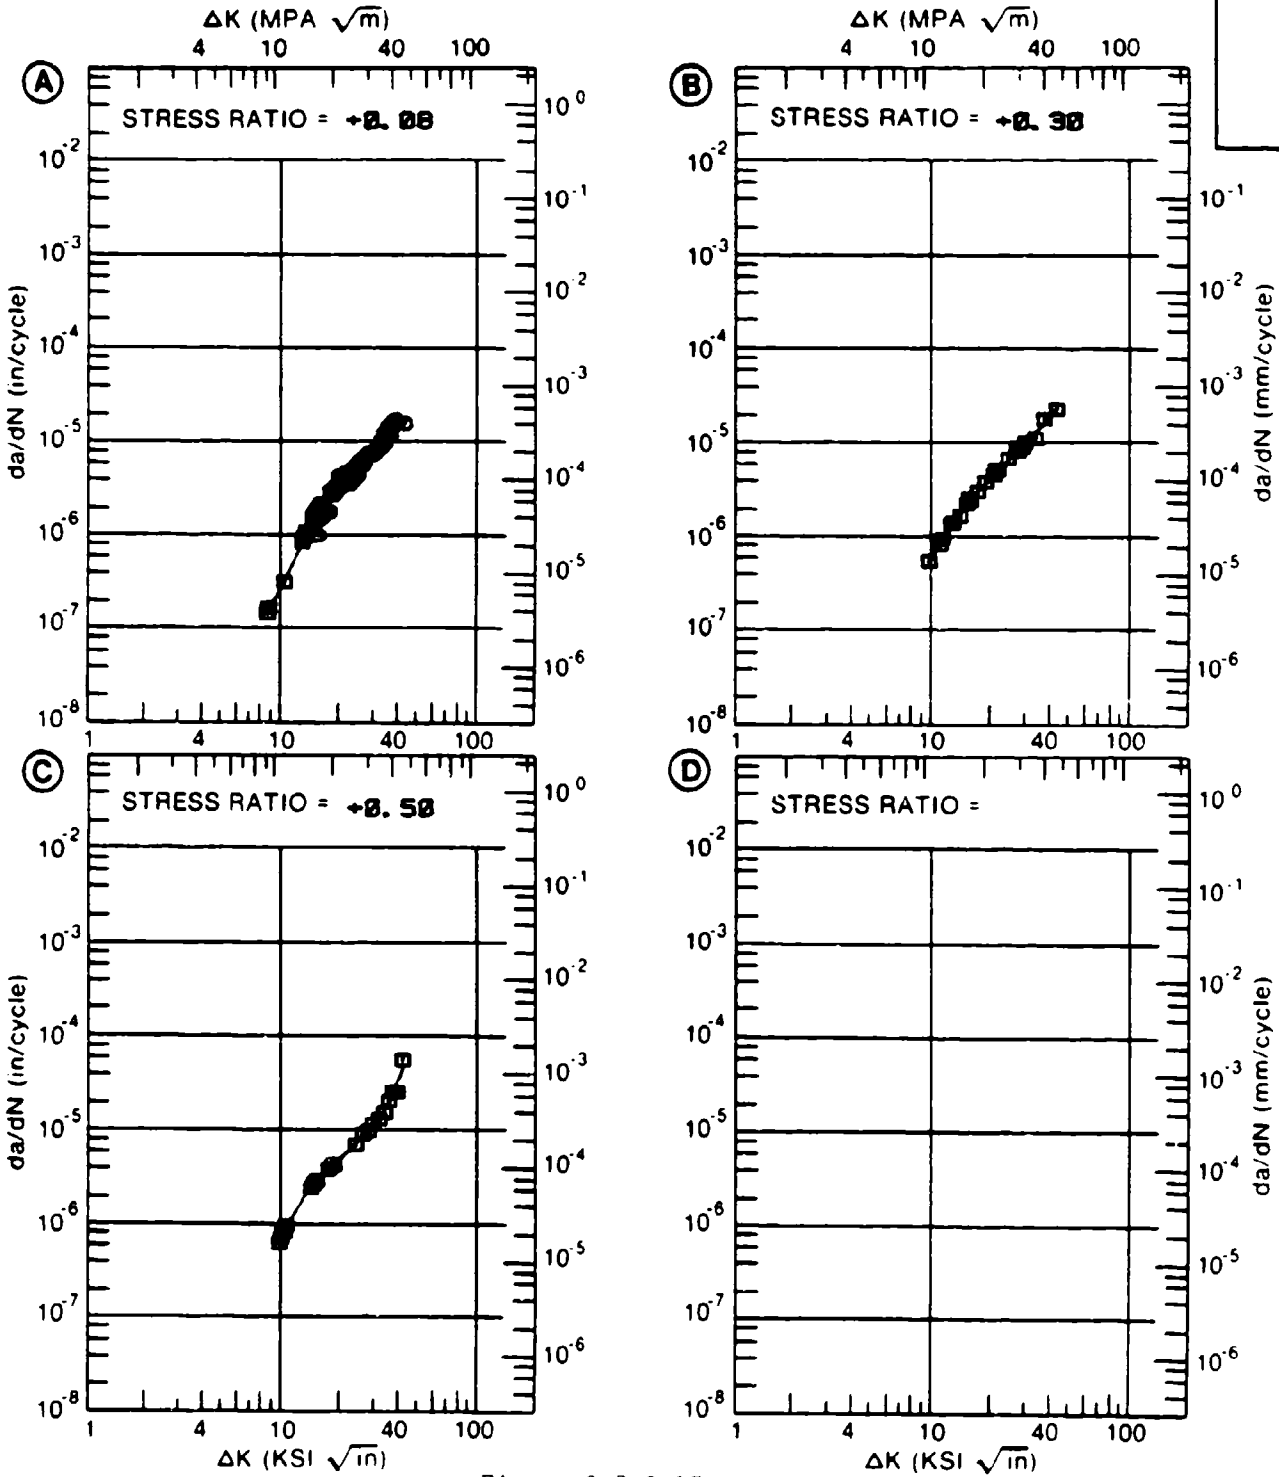


Figure 3.8.3.17

TABLE 3.8.3.18

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 3.8.3.18 INDICATING EFFECT
OF ENVIRONMENTMATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A. -1. OHZ	E=- 65 F L. H. A. -6. OHZ	E= R. T. S. C. S. -1. OHZ	
DELTA K MIN	A: 8.72	.151			
	B: 15.07		.404		
	C: 12.88			.517	
	D:				
	9.00	.177			
	10.00	.290			
	13.00	.863			.544
	16.00	1.80	.594		1.68
	20.00	3.57	1.67		5.24
	25.00	6.47	3.68		13.6
	30.00	10.0			24.5
	35.00	14.1			35.8
	40.00				45.9
	50.00				60.7
DELTA K MAX	A: 36.40	15.3			
	B: 29.64		7.95		
	C: 56.24			66.5	
	D:				
ROOT MEAN SQUARE		16.46	12.41	14.12	
PERCENT ERROR					

LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5	0.5-0.8	0.8-1.25	1.25-2.0	>2.0
			1	1	1

CONDITION/HT: H1000
 FORM: 1.50" TH ROLLED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 200.0 KSI
 ULT. STRENGTH: 216.0 KSI
 SPECIMEN THK: 0.090- 0.093"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837, 88579

STAIN.
 STEEL

PH13-8MO

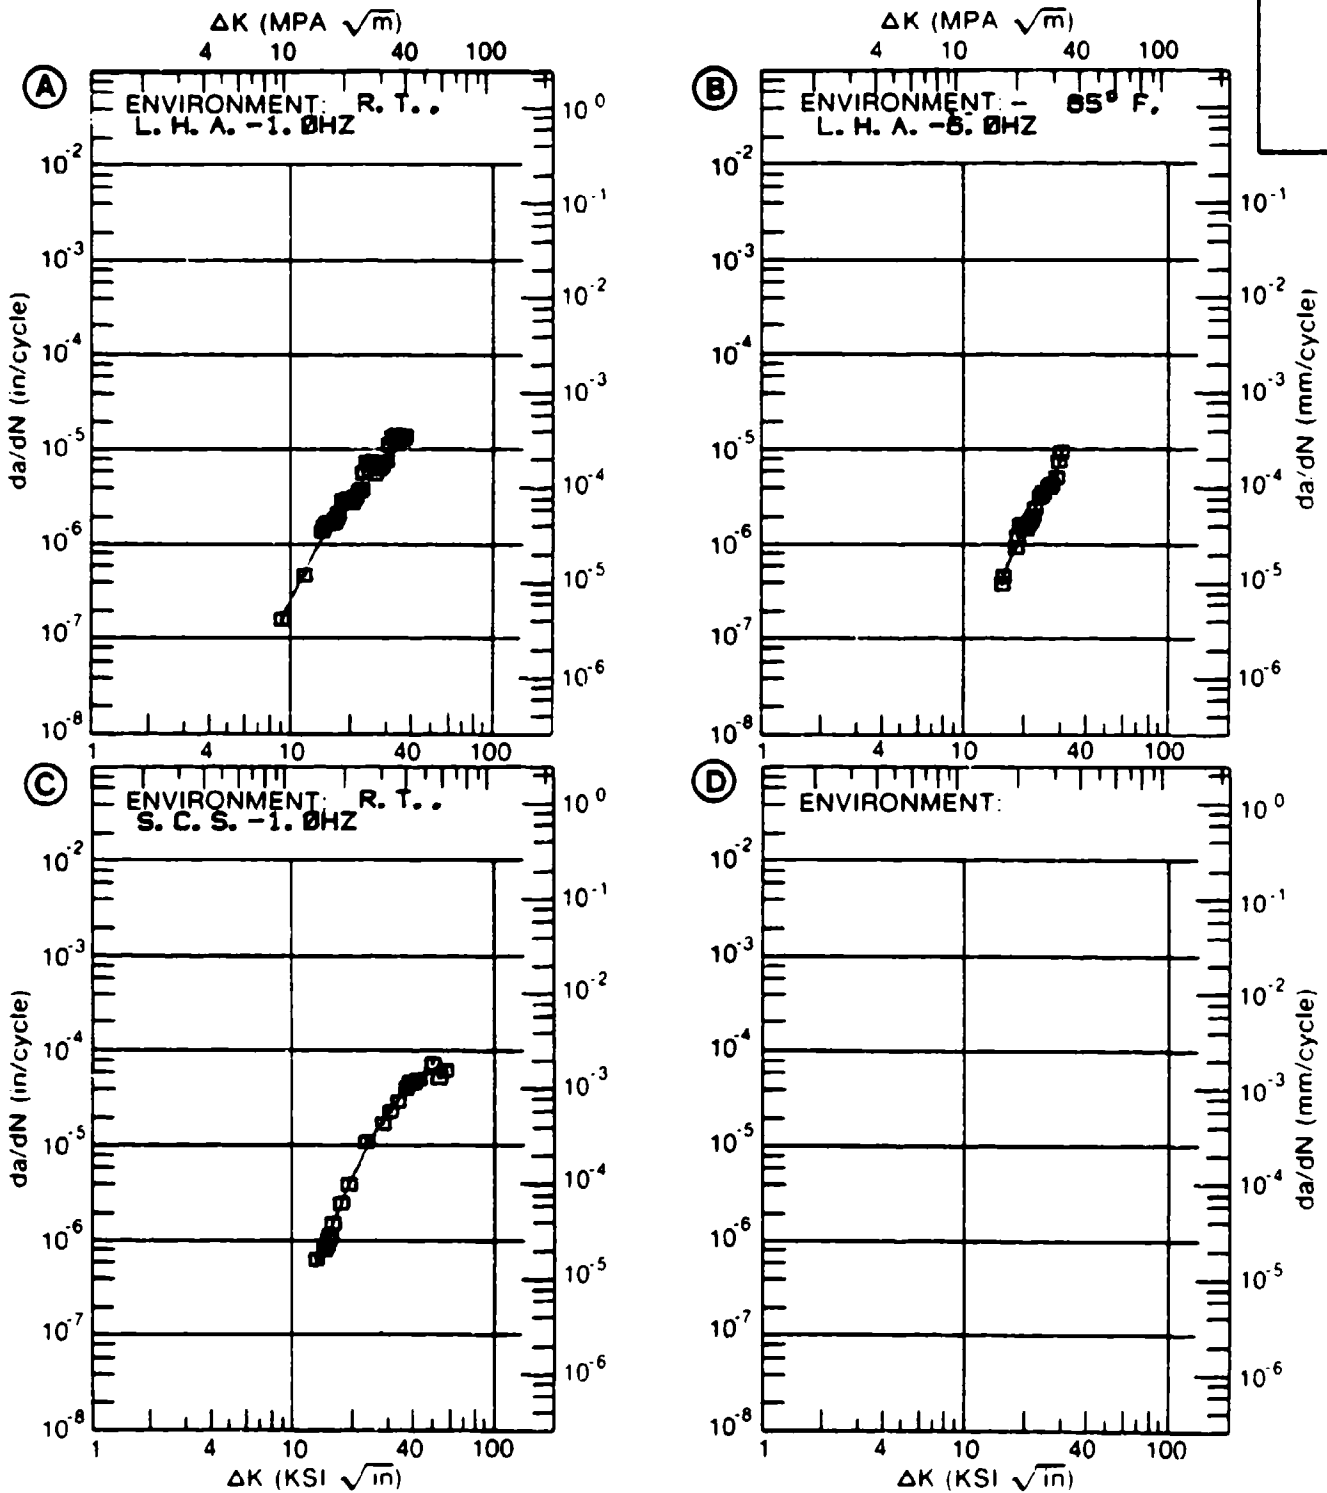


Figure 3.8.3.18

TABLE 3.8.3.19

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.19 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL PH13-8MO
CONDITION: H1000
ENVIRONMENT: R. T. , S. T. W.

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30		
DELTA K MIN	A: 11.05	.260			
	B: 8.60		.276		
	C:				
	D:				
	9.00		.372		
	10.00		.640		
	13.00	1.07	2.10		
	16.00	2.32	6.04		
	20.00	4.15	12.2		
	25.00	13.7	25.5		
	30.00	41.7	70.5		
	35.00	63.4	183.		
DELTA K MAX	A: 38.49	65.6			
	B: 36.46		225.		
	C:				
	D:				
ROOT MEAN SQUARE		24.63	15.20		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25		2		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: H1000
 FORM: 1.50" TH ROLLED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.0 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 208.0 KSI
 ULT. STRENGTH: 216.0 KSI
 SPECIMEN THK: 0.990- 1.002"
 SPECIMEN WIDTH: 7.390- 7.400"
 REFERENCES: 85837, 88579

STAIN.
STEEL

PH13-8MC

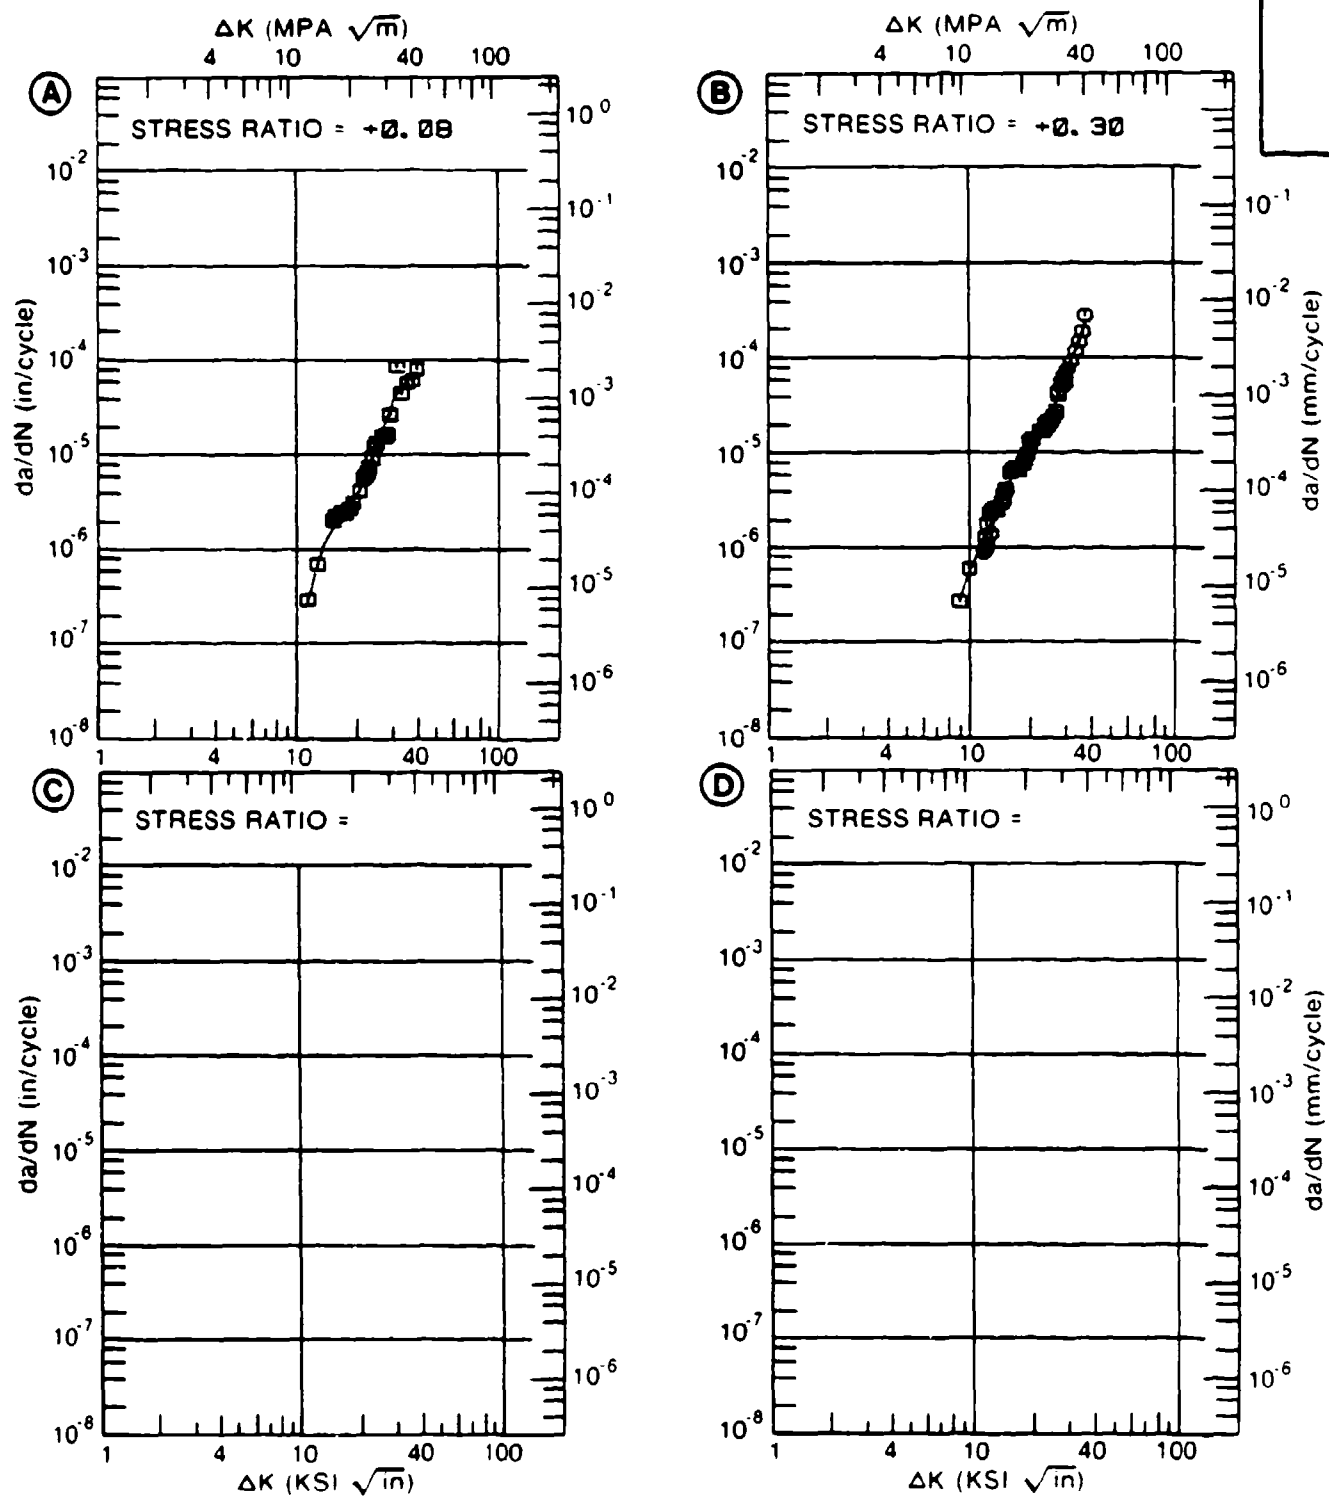


Figure 3.8.3.19

TABLE 3.8.3.20

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.8.3.20 INDICATING EFFECT
OF FREQUENCY

MATERIAL: STAINLESS STEEL PH13-BMD
CONDITION: H1000
ENVIRONMENT: R. T., S. T. W.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		F(HZ)= 0.1			
DELTA K MIN	A: 14.76	2.15			
	B:				
	C:				
	D:				
	16.00	2.95			
	20.00	6.44			
	25.00	12.9			
	30.00	22.1			
DELTA K MAX	A: 31.99	26.7			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 3.35
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) 2.0

CONDITION/HT: H1000
 FORM: 1.50" TH ROLLED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 206.0 KSI
 ULT. STRENGTH: 216.0 KSI
 SPECIMEN THK: 0.990"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 88579, 85837

STAIN.
 STEEL

PH13-8MC

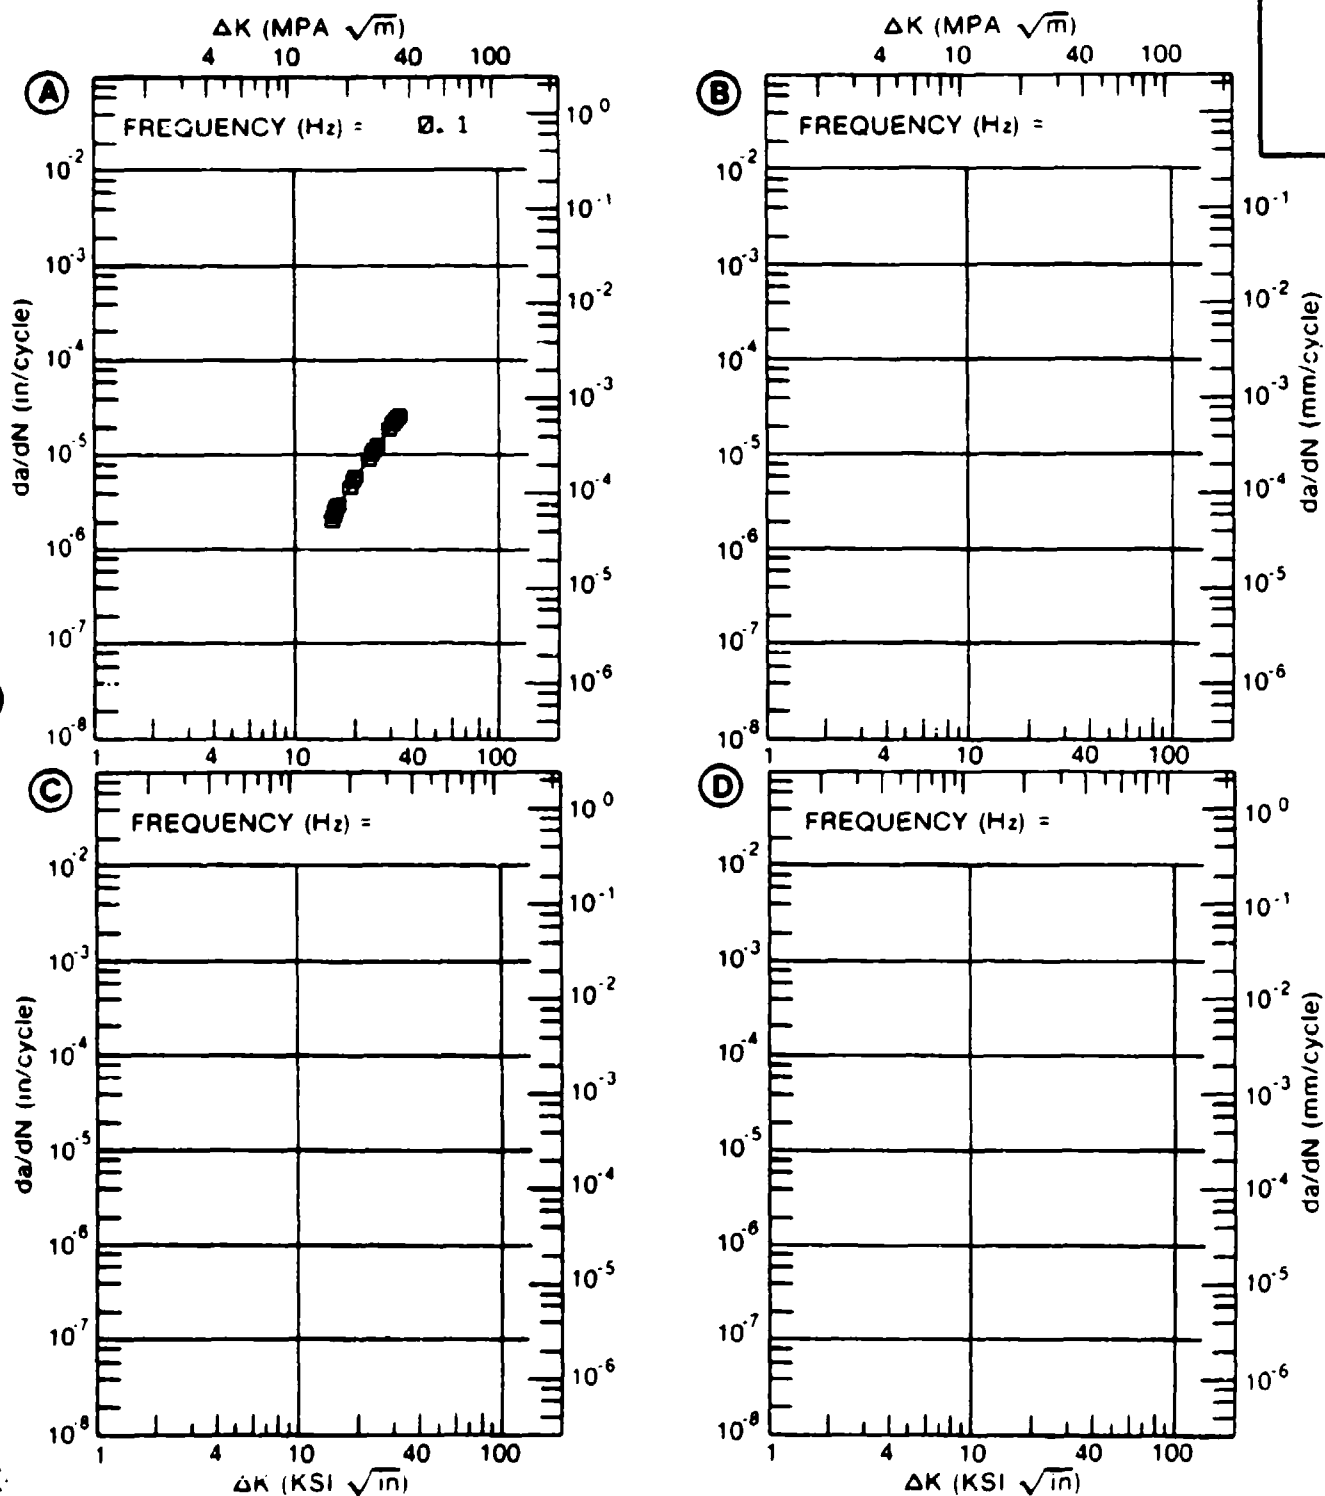


Figure 3.8.3.20

CONDITION/HT: H1000
 FORM: 1.50" TH ROLLED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 210.0 - 215.0 KSI
 ULT. STRENGTH: 219.0 KSI
 SPECIMEN THK: 0.989 - 0.993"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 88579, 85937

STAIN.
 STEEL

PH13-8MO

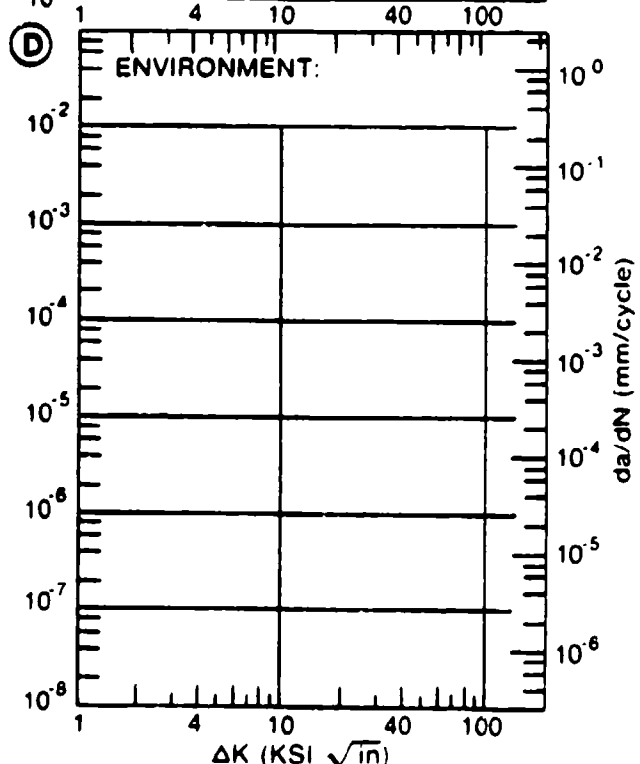
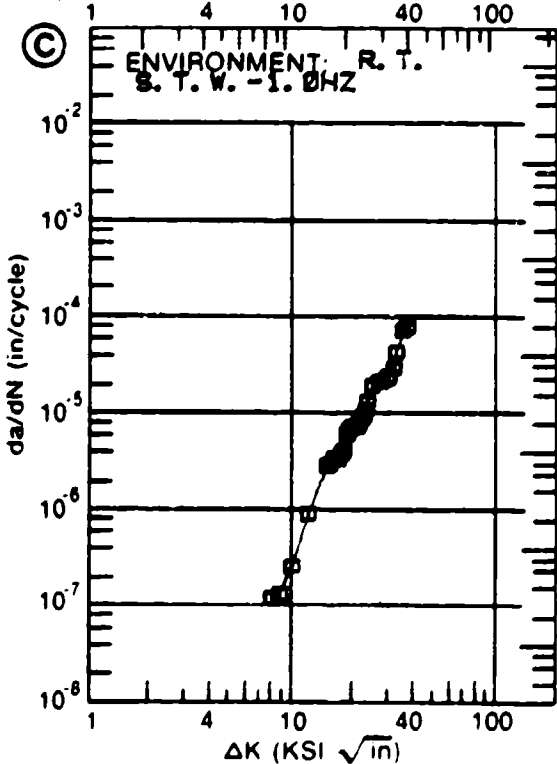
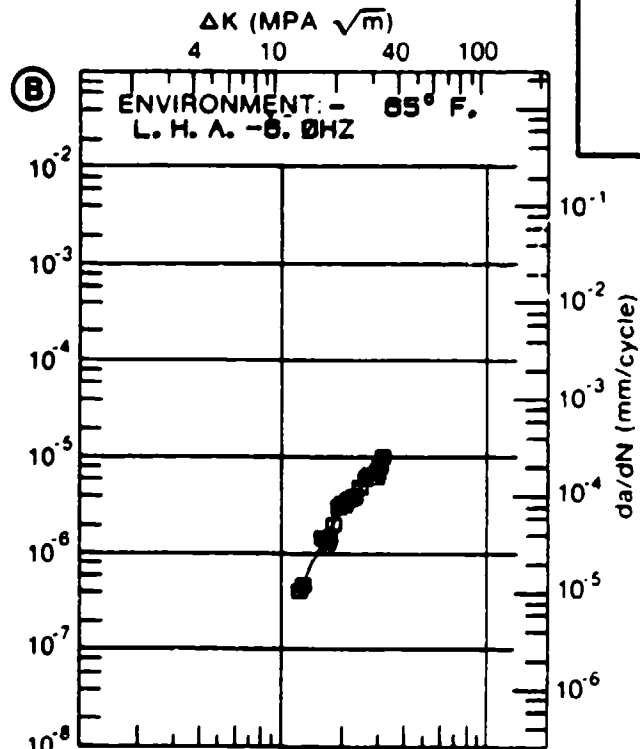
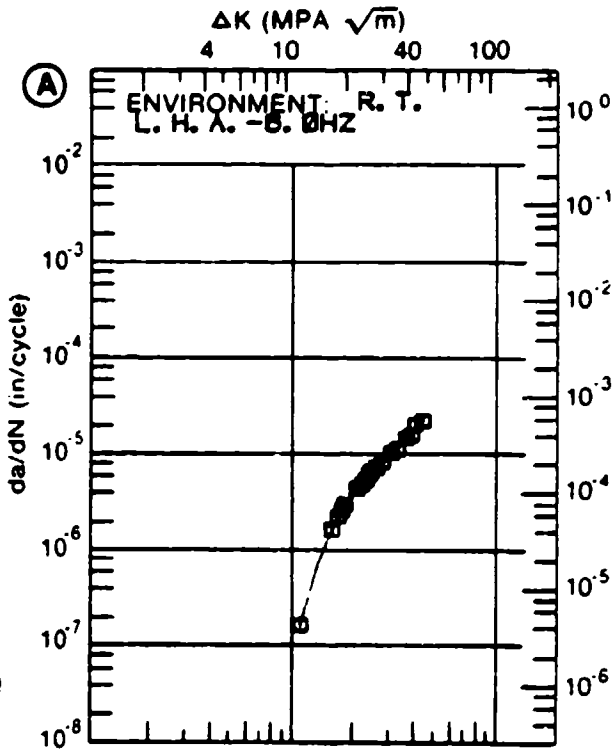


Figure 3.8.3.21

Table 3.8.3.22

CONDITION	FORM THICK (IN)		TEST TEMP (F)	SPEC YIELD OR STR (KSI)	ENVIRONMENT	WIDTH (IN)		SPECIMEN THICK DESIGN (IN)		CRACK LENGTH (IN)	K (ISCC)	MEAN (KSI)	STAN DEV	TEST TIME (MIN)	DATE REFER
	A	B				A	B	A	B						
H 950	4.00	4.00	R T	207	5.3.5 PCT NAACL	1.500	0.480	C.N.T.	73	90	73	90		> 60000	1971 84333
H 950	4.00	4.00	R T	204	0 S.T.M.	5.500	1.000	DCB	131	00	48	00		60360	1976 R1006
	4.00	4.00	R T	204	0	5.500	1.000	DCB	130	00	50	00		60320	1976 R1006
	4.00	4.00	R T	204	0	5.500	1.000	DCB	131	00	46	30		51720	1976 R1006
	4.00	4.00	R T	204	0	5.500	1.000	DCB	131	00	46	00		51720	1976 R1006
	4.00	4.00	R T	204	0	5.500	1.000	DCB	130	00	49	00		48780	1976 R1006
	4.00	4.00	R T	204	0	5.500	1.000	DCB	130	00	48	00		51720	1976 R1006
	4.00	4.00	R T	204	0	5.500	1.000	DCB	131	00	40	00		66280	1976 R1006
	4.00	4.00	R T	204	0	5.500	1.000	DCB	130	00	46	00		80320	1976 R1006
	4.00	4.00	R T	204	0	5.500	1.000	DCB	131	00	50	00		86280	1976 R1006
	4.00	4.00	R T	204	0	5.500	1.000	DCB	130	00	48	00		48780	1976 R1006
									48.0/		2.8				
H 950	2.25	2.25	R T	196	7 INDUSTRIAL ATM	2.000	1.000	CT	62	60	59	00		----	1973 86688
H 950	2.25	2.25	R T	196	7 SEACOAST ATM	2.000	1.000	CT	62	60	31	00		----	1973 86688
H 950	2.25	2.25	R T	196	7 20 PCT NAACL	2.000	1.000	CT	62	60	46	00		----	1973 86688
H1000	1.50	1.50	R T	214	0 S.T.M.	5.500	1.000	DCB	132	00	> 53	00		116820	1976 R1006
	1.50	1.50	R T	214	0	5.500	1.000	DCB	132	00	< 53	00		116820	1976 R1006
	1.50	1.50	R T	214	0	5.500	1.000	DCB	132	00	55	00		120840	1976 R1006
	1.50	1.50	R T	214	0	5.500	1.000	DCB	132	00	> 52	00		120840	1976 R1006
	1.50	1.50	R T	214	0	5.500	1.000	DCB	132	00	< 54	00		86280	1976 R1006
H1000	1.50	1.50	R T	213	0 S.T.M.	5.500	1.000	DCB	132	00	> 54	00		116820	1976 R1006
	1.50	1.50	R T	213	0	5.500	1.000	DCB	132	00	> 53	00		116820	1976 R1006
	1.50	1.50	R T	213	0	5.500	1.000	DCB	132	00	< 53	00		116820	1976 R1006
H1000	1.00	4.00	R T	215	0 S.T.M.	2.544	0.998	MDL	1.207	-----	88	10		> 60420	1978 00009
	4.00	4.00	R T	201	0	5.500	1.000	DCB	-----	127	00	> 74	00	51720	1976 R1006
	4.00	4.00	R T	201	0	5.500	1.000	DCB	-----	127	00	> 80	00	80320	1976 R1006
H1000	1.00	1.00	R T	215	0 3.5% NAACL	2.548	0.998	MDL	1.250	-----	82	30		> 60420	1978 00009
	1.00	1.00	R T	215	0	2.549	0.998	MDL	1.110	-----	94	80		> 60420	1978 00009
									88.6/		8.8				
H1000	1.00	1.00	R T	216	0 S.T.M.	2.544	0.999	MDL	1.048	-----	99	30		> 60420	1978 00009
	1.00	1.00	R T	216	0	2.549	0.999	MDL	1.048	-----	99	60		> 60420	1978 00009
	4.00	4.00	R T	198	0	5.500	1.000	DCB	-----	125	00	> 49	00	80320	1976 R1006
	4.00	4.00	R T	198	0	5.500	1.000	DCB	-----	125	00	> 49	00	80320	1976 R1006

Table 3.8.3.22 (Continued)

CONDITION	PRODUCT FORM	THICK (IN)	TEST TEMP (F)	SPEC YIELD STR (KSI)	ENVIRONMENT	SPECIMEN		WIDTH (IN)	THICK (IN)	DESIGN (IN)	CRACK LENGTH (IN)	K(I0)	K(I50RT IN)	MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
						M	B										
H1000	FB	4.00	R T	T-L	198.0	S.T.M.	5.900	1.000	DCB	---	125.00	>	46.00			63520	1976 R1006
		4.00			179.0		5.900	1.000	DCB	---	125.00	>	71.00			31720	1976 R1006
		4.00			198.0		5.900	1.000	DCB	---	125.00	>	68.00	99.6/	0.1	31720	1976 R1006
H1000	FB	1.00	R T	T-L	216.0	3.5Z NaCl	2.945	0.998	MOL	1.880	---	---	63.20			60420	1978 CD009
		1.00			216.0		2.947	0.999	MOL	1.250	---	---	85.90	74.4/	15.8	60420	1978 CD009
H1000	RR	1.50	R T	L-T	208.0	F.C.S.	5.500	1.000	DCB	---	132.00	>	75.00			75180	1976 R1006
H1000	RB	1.50	R T	L-T	208.0	S.C.B.	5.500	1.000	DCB	---	132.00	>	87.00			60180	1976 R1006
		1.50			208.0		5.500	1.000	DCB	---	132.00	>	70.00			75240	1976 R1006
H1000	RB	1.50	R T	L-T	208.0	S.T.M.	5.500	1.000	DCB	---	132.00	>	73.00			86280	1976 R1006
		1.50			208.0		5.500	1.000	DCB	---	132.00	>	73.00			116820	1976 R1006
		1.50			208.0		5.500	1.000	DCB	---	132.00	>	70.00			116820	1976 R1006
H1000	RB	1.50	R T	L-T	215.0	S.T.M.	5.500	1.000	DCB	---	132.00	>	73.00			116820	1976 R1006
		1.50			215.0		5.500	1.000	DCB	---	133.00	>	63.00			86280	1976 R1006
		1.50			215.0		5.500	1.000	DCB	---	133.00	>	63.00			116820	1976 R1006
H1050	B	2.25	R T	T-L	178.5	INDUSTRIAL ATM	2.000	1.000	CT	---	87.80		83.00			---	1973 B6688
		2.25	R T	T-L	178.5	SEACAST ATM	2.000	1.000	CT	---	87.80		44.00			---	1973 B6688
		2.25	R T	T-L	178.5	20 PCT NaCl	2.000	1.000	CT	---	87.80		65.00			---	1973 B6688
RH 950	BR	1.50	R T	L-S	219.0	S.T.M.	5.500	1.000	CT	---	98.00	>	50.00			120960	1976 R1006
		1.50			217.0		5.500	1.000	CT	---	97.00	>	54.00			120960	1976 R1006
		1.50			219.0		5.500	1.000	CT	---	98.00	>	51.00			120960	1976 R1006
RH 975	BR	1.50	R T	L-S	216.0	S.T.M.	5.500	1.000	CT	---	97.00	>	67.00			120960	1976 R1006
		1.50			219.0		5.500	1.000	CT	---	98.00	>	58.00			120960	1976 R1006
		1.50			216.0		5.500	1.000	CT	---	97.00	>	67.00			120960	1976 R1006

Table 3.8.3.22 (Continued)

CONDITION	STAINLESS STEEL PH13-8MO K (ISCC)										TEST TIME (MIN)	DATE REFER	
	FURN	THICK (IN)	TEMP (F)	SPECS	YIELD STR (KSI)	ENVIRONMENT	SPECIMEN		CRACK				STAN DEV
							WIDTH (IN)	THICK (IN)	DESIGN (IN)	LENGTH (IN)			
RH1000	BR	1.50	R.T.	L-S	215.0	S.T.M	5.500	1.000	CT	96.00	101.00	120960	1976 R1006
		1.50			215.0		5.500	1.000	CT	96.00	92.00	120960	1976 R1006
		1.50			218.0		5.500	1.000	CT	97.00	83.00	120960	1976 R1006
TYS=140KSI	P	1.00	R.T.	T-L	140.0	3.5 PCT NAACL	1.000	CANT*		180.00	170.00*	1972	83613
TYS=180KSI	P	1.00	R.T.	T-L	180.0	3.5 PCT NAACL	1.000	CANT*		190.00	160.00*	1972	83613
TYS=190KSI	P	1.00	R.T.	T-L	190.0	3.5 PCT NAACL	1.000	CANT*		180.00	130.00*	1972	83613
TYS=200KSI	P	1.00	R.T.	T-L	200.0	3.5 PCT NAACL	1.000	CANT*		190.00	155.00*	1972	83613
TYS=210KSI	P	1.00	R.T.	T-L	210.0	3.5 PCT NAACL	1.000	CANT*		135.00	120.00	1972	83613

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.51KIBCC/TYS>SQUARED

Table 3.9.2.1

CONDITION	PROJECT		TEST SPEC	YIELD STR (KSI)	SPECIMEN		CRACK LENGTH		GROSS STRESS		K(AFP) STAM		K(C) STAM		
	FORM	THICK (IN)			THICK (IN)	WIDTH (IN)	W	B	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	MEAN (IN)	DEV (IN)	MEAN (IN)
SRH1050	S	0.03	63	L-T	174.5	24.040	0.033	3.990	---	72.60	231.63	---	---	---	1964 97573
SRH1050	S	0.03	R T	L-T	174.5	7.990	0.025	2.010	---	118.10	218.44*	---	---	---	1964 97573
SRH1050	S	0.03	R T	L-T	174.5	24.020	0.025	3.000	---	95.90	210.21	---	---	---	1964 97573
		0.03			174.5	24.040	0.025	4.000	---	71.90	229.61	223.7/11.7	---	---	1964 97573
SRH1050	S	0.05	R T	L-T	196.6	24.010	0.050	4.000	---	92.10	294.19	---	---	---	1964 97573
SRH1050	S	0.09	R T	L-T	197.4	24.100	0.073	6.000	---	115.70	369.42	---	---	---	1964 97573

BUCKLING OF CRACK EDGES RESTRAINED

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV

Table 3.10.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
STAINLESS STEEL ALLOY PH19-7MO AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (AS1 SORTING) DEVIATION		COLLED JAW
	L-I	I-I	
RH 930	-----	30.6 ± 0.1 (2)	-----
RH1050	-----	40.2 ± 1.9 (3)	-----

Table 3.10.2.1

CONDITION	STAINLESS STEEL PH19-7MO K(IIC)										K(IIC) STAN MEAN DEV	DATE	REFER
	FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	K(IIC)/TVS) ^{2.5*} (IN)			
RH 950	RP	1.25	R T	T-1	204.0	2.000	1.000	CT	1.029	0.06	30.50	0.1	1973 86688
		1.25			204.0	2.000	1.000	CT	1.007	0.06	30.70	30.6/	1973 86688
RH1050	RP	1.25	R T	T-L	195.0	2.000	1.000	CT	1.019	0.10	38.50		1973 86688
		1.25			195.0	2.000	1.000	CT	1.010	0.11	40.70		1973 86688
		1.25			195.0	2.000	1.000	CT	1.006	0.11	41.30	40.2/	1973 86688

Table 3.10.3.1

CONDITION	FORM	THICK (IN)	YIELD STR (KSI)	TEST TEMP (F)	ENVIRONMENT	WIDTH (IN)	THICK (IN)	DESIGN (IN)	CRACK LENGTH (IN)	K (I SCC)	MEAN (IN)	STAN DEV	TEST TIME (MIN)	DATE REFER
RH 950	B	1.75	196	R.T.	3.5 PCT NaCl	1.500	0.480	CANT	31.50	14.00			> 30000	1971 84333
TH1050	B	1.75	167	R.T.	3.5 PCT NaCl	1.500	0.480	CANT	33.60	18.50			> 60000	1971 84333

Table 3.11.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
STAINLESS STEEL ALLOY 19-3PH AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION	(NUMBER OF SPECIMENS)
	FORGING	
CONDITION/HT	L-I	B-I
Y _S =150-165KSI	-----	94.8 ± 6.9 (3)
	ROLLED BAR	
CONDITION/HT	L-I	B-I
H 900	-----	72.7 ± 4.9 (6)

Table 3.11.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL 15-3PH

TEST CONDITIONS

SPECIMEN
ORIENTATION: T-LENVIRONMENT: H. H. A.
AT R. T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)				
					2.5	5	10	20	50
TUS-150-165KSI	BILLET	-1.00						3.93	45.6
TUS-150-165KSI	BILLET	-0.20						3.05	33.6
TUS-150-165KSI	BILLET	0.04						2.92	33.6
TUS-150-165KSI	BILLET	0.40					0.73	5.18	

Table 3.11.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL 15-5PH

TEST CONDITIONS

SPECIMEN
ORIENTATION S-LENVIRONMENT: H.H.A.
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
TUS-150-165KSI	BILLET	-1.00						4.78	51.6	
TUS-150-165KSI	BILLET	-0.20						3.46	39.8	
TUS-150-165KSI	BILLET	0.04						3.16	37.9	
TUS-150-165KSI	BILLET	0.40						6.02		

Table 3.11.2.1

CONDITION	STAINLESS STEEL 19-9PH										K(IIC)		DATE	REFER
	--PRODUCT-- FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5" (IN)	K(IIC) (KSI/√IN)	K(IIC) MEAN (KSI/√IN)		
H 900	RB	2.25	R.T.	T-L	171.0	4.000	2.000	CT	2.037	0.43	70.90	70.90	1973	86688
		2.25			171.0	4.000	2.000	CT	2.064	0.42	70.50	70.50	1973	86688
		2.25			171.0	2.000	1.000	CT	1.040	0.38	66.50	66.50	1973	86688
		2.25			171.0	4.000	2.000	CT	1.049	0.46	73.10	73.10	1973	86688
		2.25			171.0	4.000	2.000	CT	2.068	0.54	79.40	79.40	1973	86688
H 900	RB	4.00	R.T.	L-R	185.0	2.000	1.000	NE	1.051	0.49	75.80	72.71	1973	86688
									1.000	0.55	86.90	86.90	1972	84212
TYS=150-165KSI F			R.T.	T-L	155.0	3.000	1.500	CT	---	1.09	102.50	102.50	1978	8M007
					155.0	3.000	1.500	CT	---	0.89	92.70	92.70	1978	8M007
					155.0	3.000	1.500	CT	---	0.83	89.20	94.81	1978	8M007

TABLE 3.11.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 3.11.3.1 INDICATING EFFECT
OF ENVIRONMENTMATERIAL: STAINLESS STEEL 15-5PH
CONDITION: H1025

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR-10. OHZ		E= R. T. 3. 5%NACL-1. OHZ	
DELTA K	A: 30.17	8.27			
MIN	B: 17.18		5.06		
	C:				
	D:				
	20.00		9.97		
	25.00		15.7		
	30.00		20.3		
	35.00	15.0			
	40.00	18.0			
	50.00	22.0			
	60.00	29.7			
	70.00	41.2			
	80.00	56.1			
	90.00	74.1			
	100.00	94.2			
DELTA K	A: 124.79	146.			
MAX	B: 30.88		21.5		
	C:				
	D:				
ROOT MEAN SQUARE		8.12	19.17		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2	1		
SUMMARY	1.25-2.0				
(NP/NA)	2.0				

CONDITION/HT: H1025
 FORM: 1.50" TH BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.50
 FREQUENCY:

YIELD STRENGTH: 150.7 KSI
 ULT. STRENGTH: 156.2 KSI
 SPECIMEN THK: 1.500"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: 92270

STAIN.
 STEEL

15-SPH

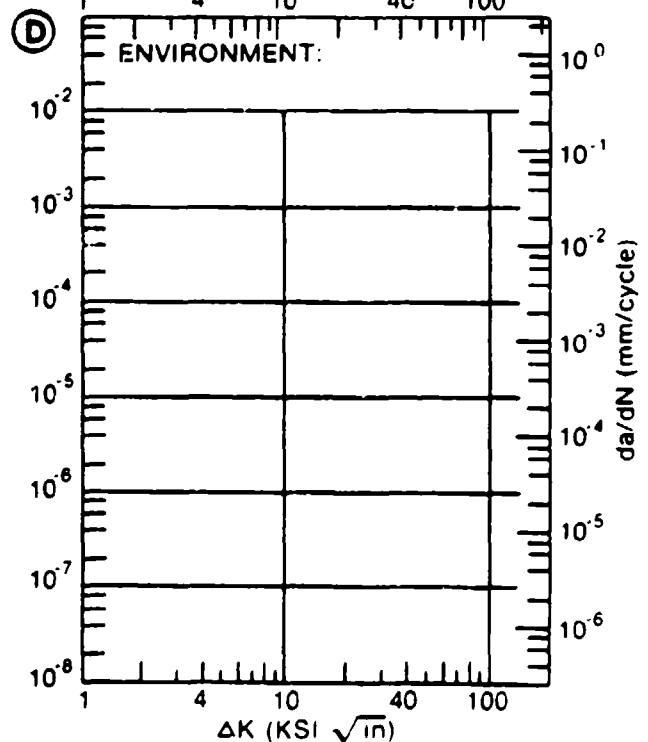
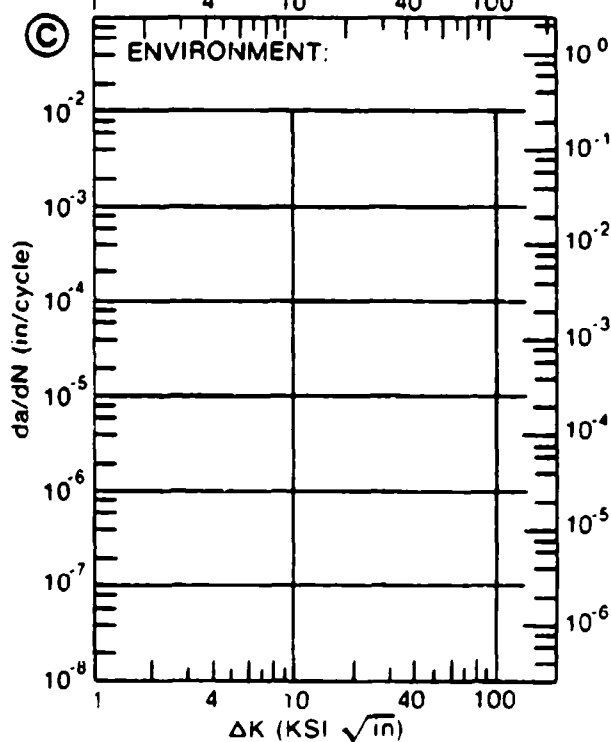
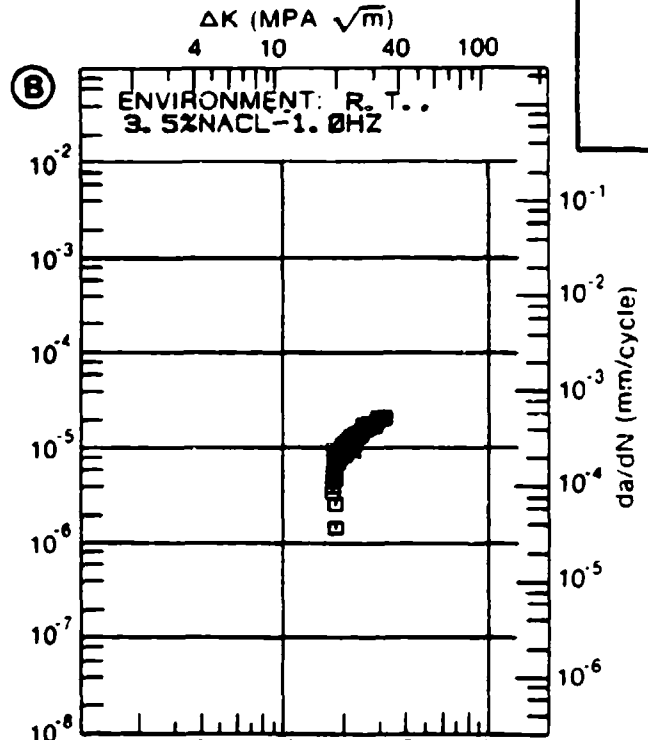
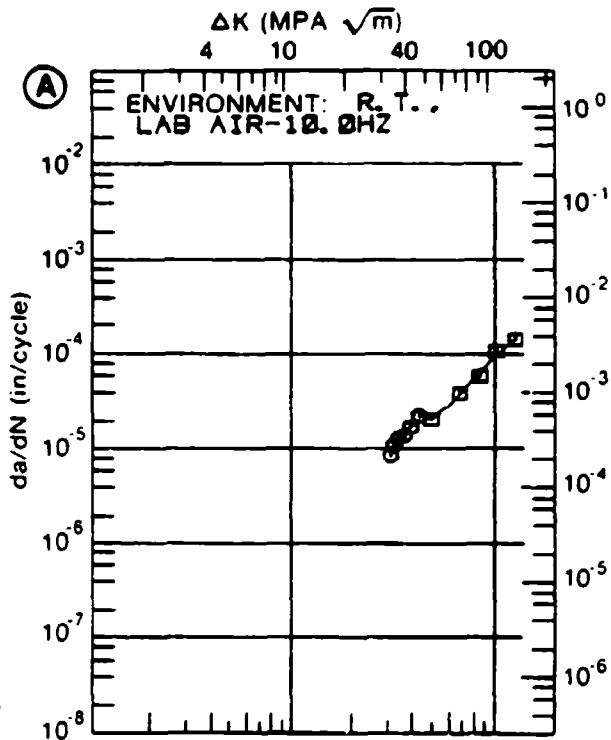


Figure 3.11.3.1

TABLE 3.11.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.11.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL 15-5PH
CONDITION: H1025

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN./CYCLE)			
	A	B	C	D
	E= R. T. LAB AIR			
DELTA K MIN	A: 28.88	1.50		
	B: 30.00	1.73		
	C: 35.00	3.08		
	D: 40.00	5.37		
		50.00	15.3	
		60.00	31.1	
		70.00	48.6	
		80.00	70.0	
		90.00	102.	
		100.00	155.	
DELTA K MAX	A: 107.17	219.		
	B:			
	C:			
	D:			

ROOT MEAN SQUARE 42.67
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: H1025
 FORM: 1.50" TH BAR
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.05
 FREQUENCY: 10.00 HZ

YIELD STRENGTH: 151.2 KSI
 ULT. STRENGTH: 156.1 KSI
 SPECIMEN THK: 1.500"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: 92270

STAIN.
 STEEL

15-5PH

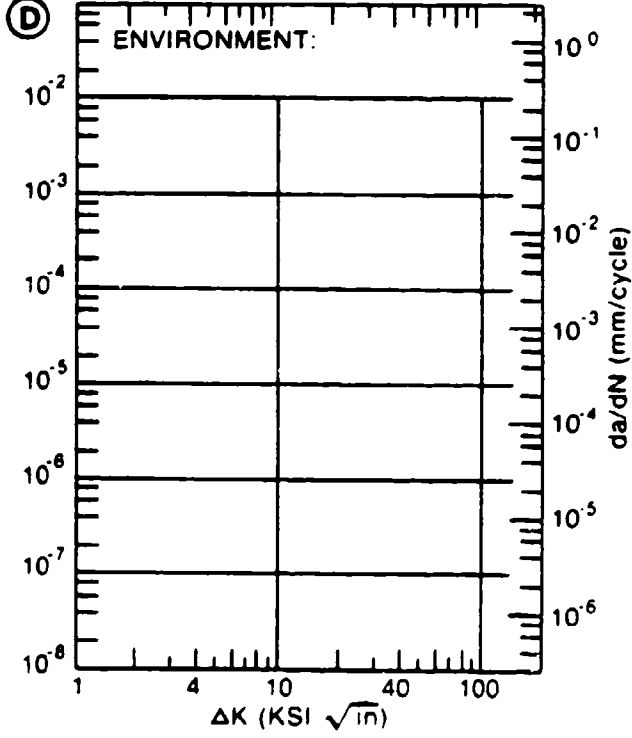
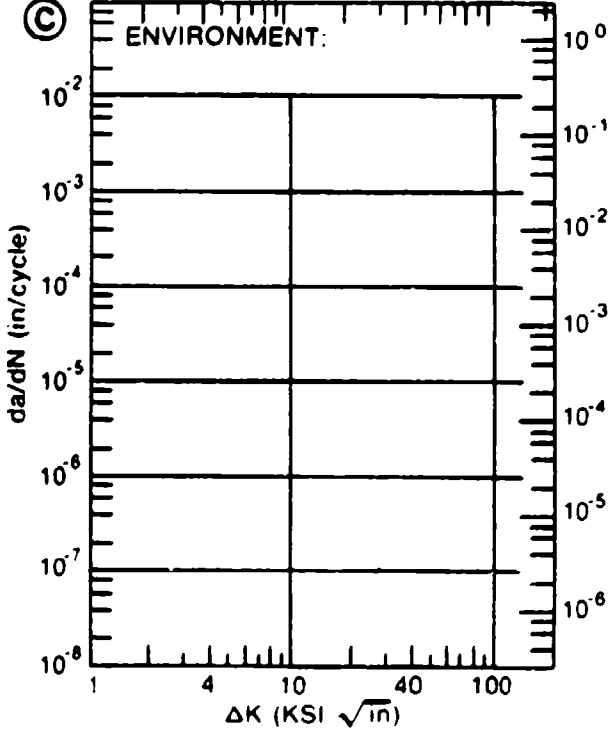
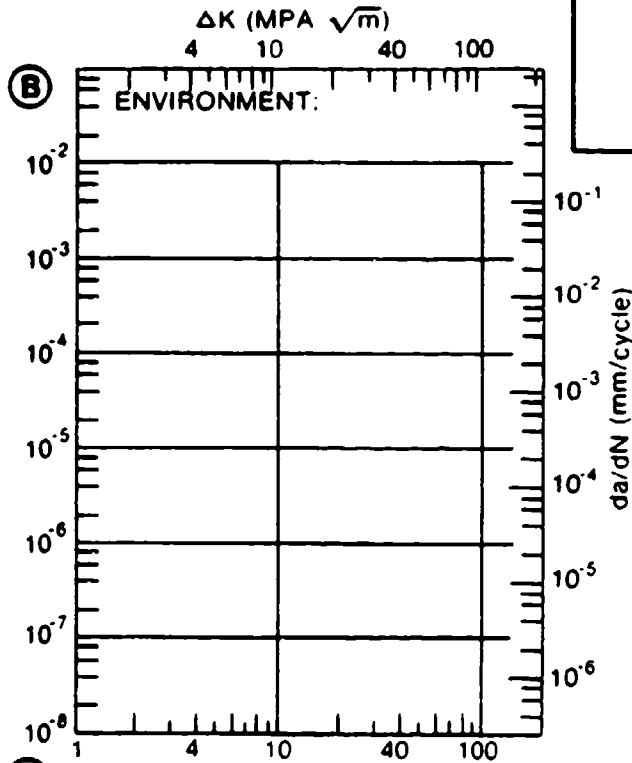
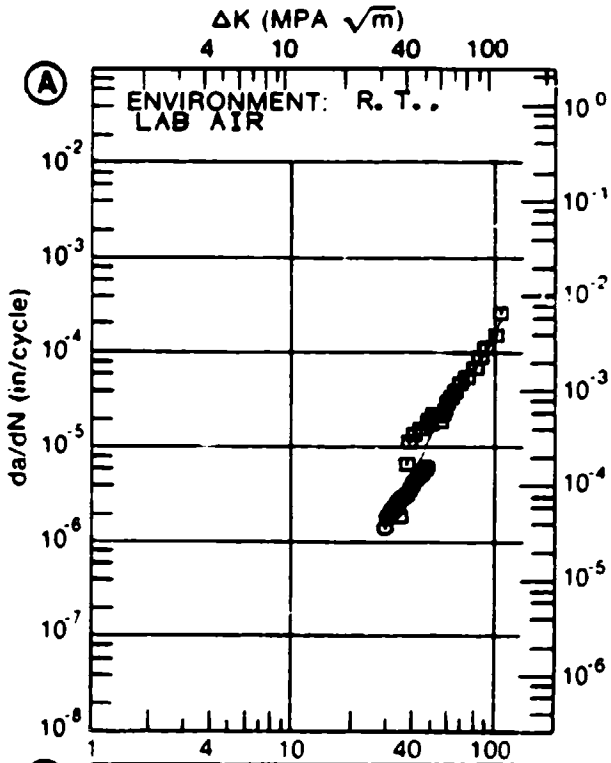


Figure 3.11.3.2

TABLE 3.11.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.11.3.3 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 15-5PH
CONDITION: H1025
ENVIRONMENT: R. T. , 3.5% NaCl

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.05	R=+0.50		
DELTA K	A: 33.23	17.9			
MIN	B: 24.76		13.2		
	C:				
	D:				
	25.00		13.4		
	30.00		18.6		
	35.00	19.9	26.7		
	40.00	25.6	36.7		
	50.00	39.4			
	60.00	60.4			
DELTA K	A: 63.17	69.7			
MAX	B: 43.53		44.1		
	C:				
	D:				
ROOT MEAN SQUARE		2.30	4.38		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: H1025
 FORM: 1.50" TH BAR
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 151.2 KSI
 ULT. STRENGTH: 158.1 KSI
 SPECIMEN THK: 1.500"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: 02270

STAIN.
 STEEL

15-5PH

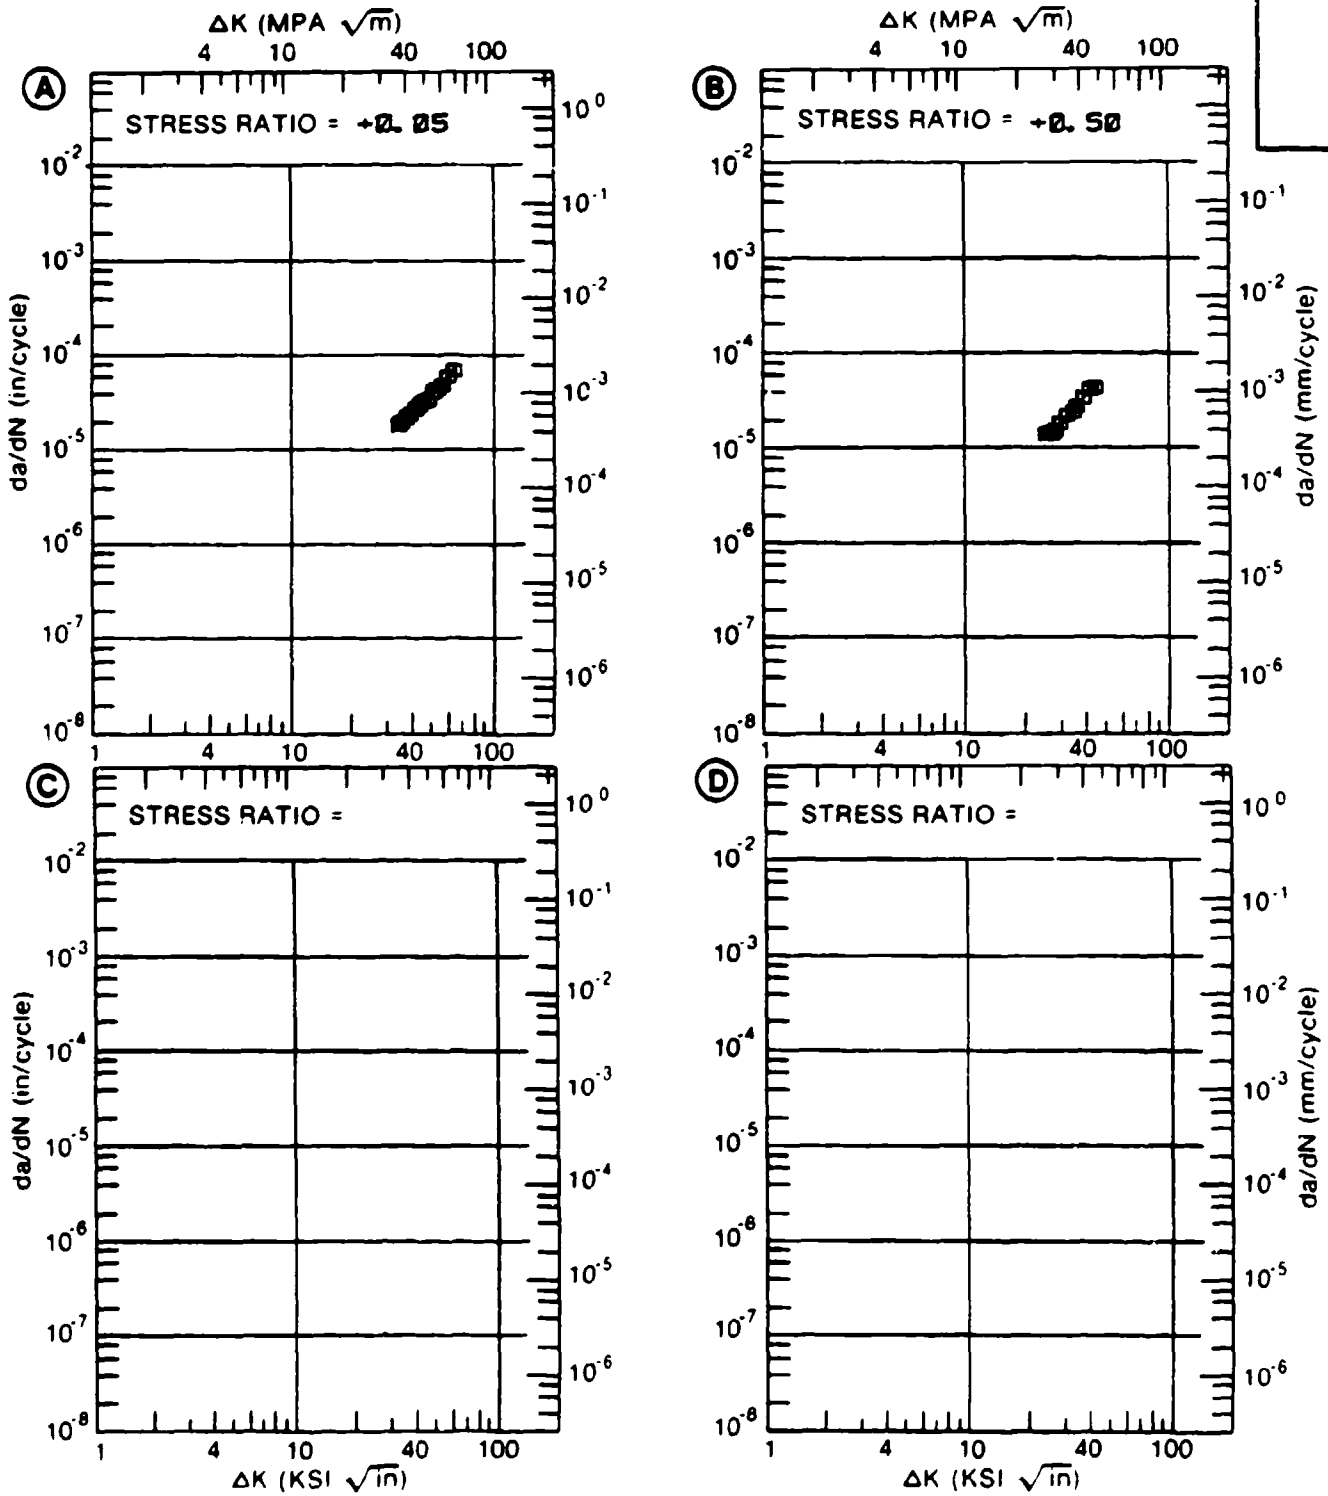


Figure 3.11.3.3

TABLE 3.11.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.11.3.4 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 15-5PH
CONDITION: TUS=150-165KSI
ENVIRONMENT: R. T., H. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=-1.00	R=-0.20	R=+0.04	R=+0.40
A:	12.00	.706			
B:	14.00		.915		
C:	13.44			.738	
D:	9.60				.629
	10.00				.739
	13.00	.985			1.76
	16.00	2.07	1.52	1.45	3.05
	20.00	3.93	3.05	2.92	5.18
	25.00	6.82	5.43	5.22	8.94
	30.00	10.5	8.38	8.09	14.9
	35.00	15.5	12.2	11.8	24.9
	40.00	22.3	17.2	16.8	42.2
	50.00	45.6	33.6	33.6	
	60.00	94.6	66.2	67.8	
	70.00		133.	140.	
A:	70.00	200.			
B:	80.00		272.		
C:	76.80			231.	
D:	48.00				101.
ROOT MEAN SQUARE		1.30	.62	2.28	2.82
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: TUS-150-165KSI
 FORM: 0.50" TH BILLET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY:
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: BW005

STAIN.
 STEEL

15-5PH

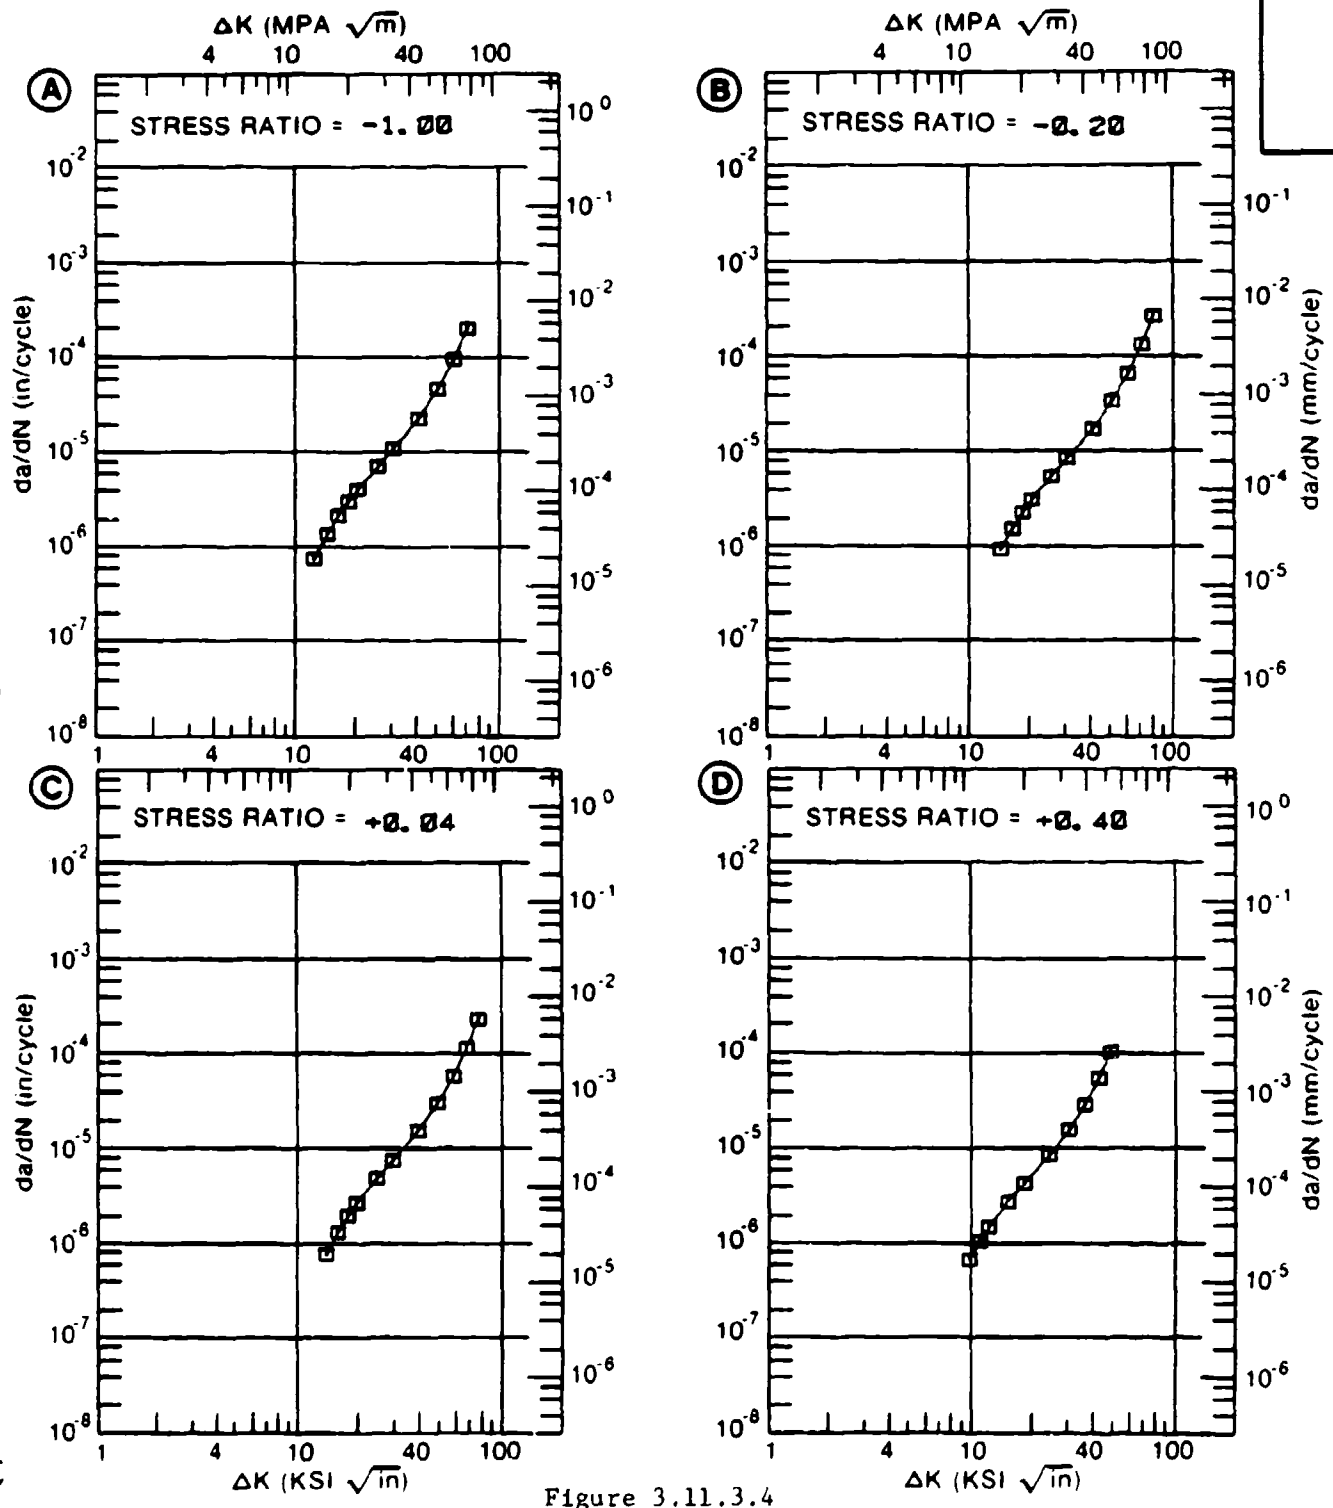


Figure 3.11.3.4

TABLE 3.11.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.11.3.5 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 15-5PH
CONDITION: TUS=150-165KSI
ENVIRONMENT: R. T., H. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN./CYCLE)			
	A R=-1.00	B R=-0.20	C R=+0.04	D R=+0.40
A: 14.00	1.67			
B: 14.00		1.31		
C: 15.36			1.56	
D: 10.80				1.24
13.00				2.09
16.00	2.61	1.92	1.75	3.51
20.00	4.78	3.46	3.16	6.02
25.00	8.05	5.99	5.45	10.8
30.00	12.2	9.38	8.51	18.9
35.00	17.7	13.9	12.7	33.0
40.00	25.3	20.1	18.5	58.0
50.00	51.6	39.8	37.9	
60.00			76.5	
A: 60.00	108.			
B: 60.00		76.0		
C: 67.20			126.	
D: 48.00				146.
ROOT MEAN SQUARE PERCENT ERROR	7.16	1.94	2.77	4.04

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: TUS-150-165KSI
 FORM: Ø. 50" TH BILLET
 SPECIMEN TYPE: CCP
 ORIENTATION: S-L
 FREQUENCY:
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: BWØØ4

STAIN.
 STEEL

15-5PH

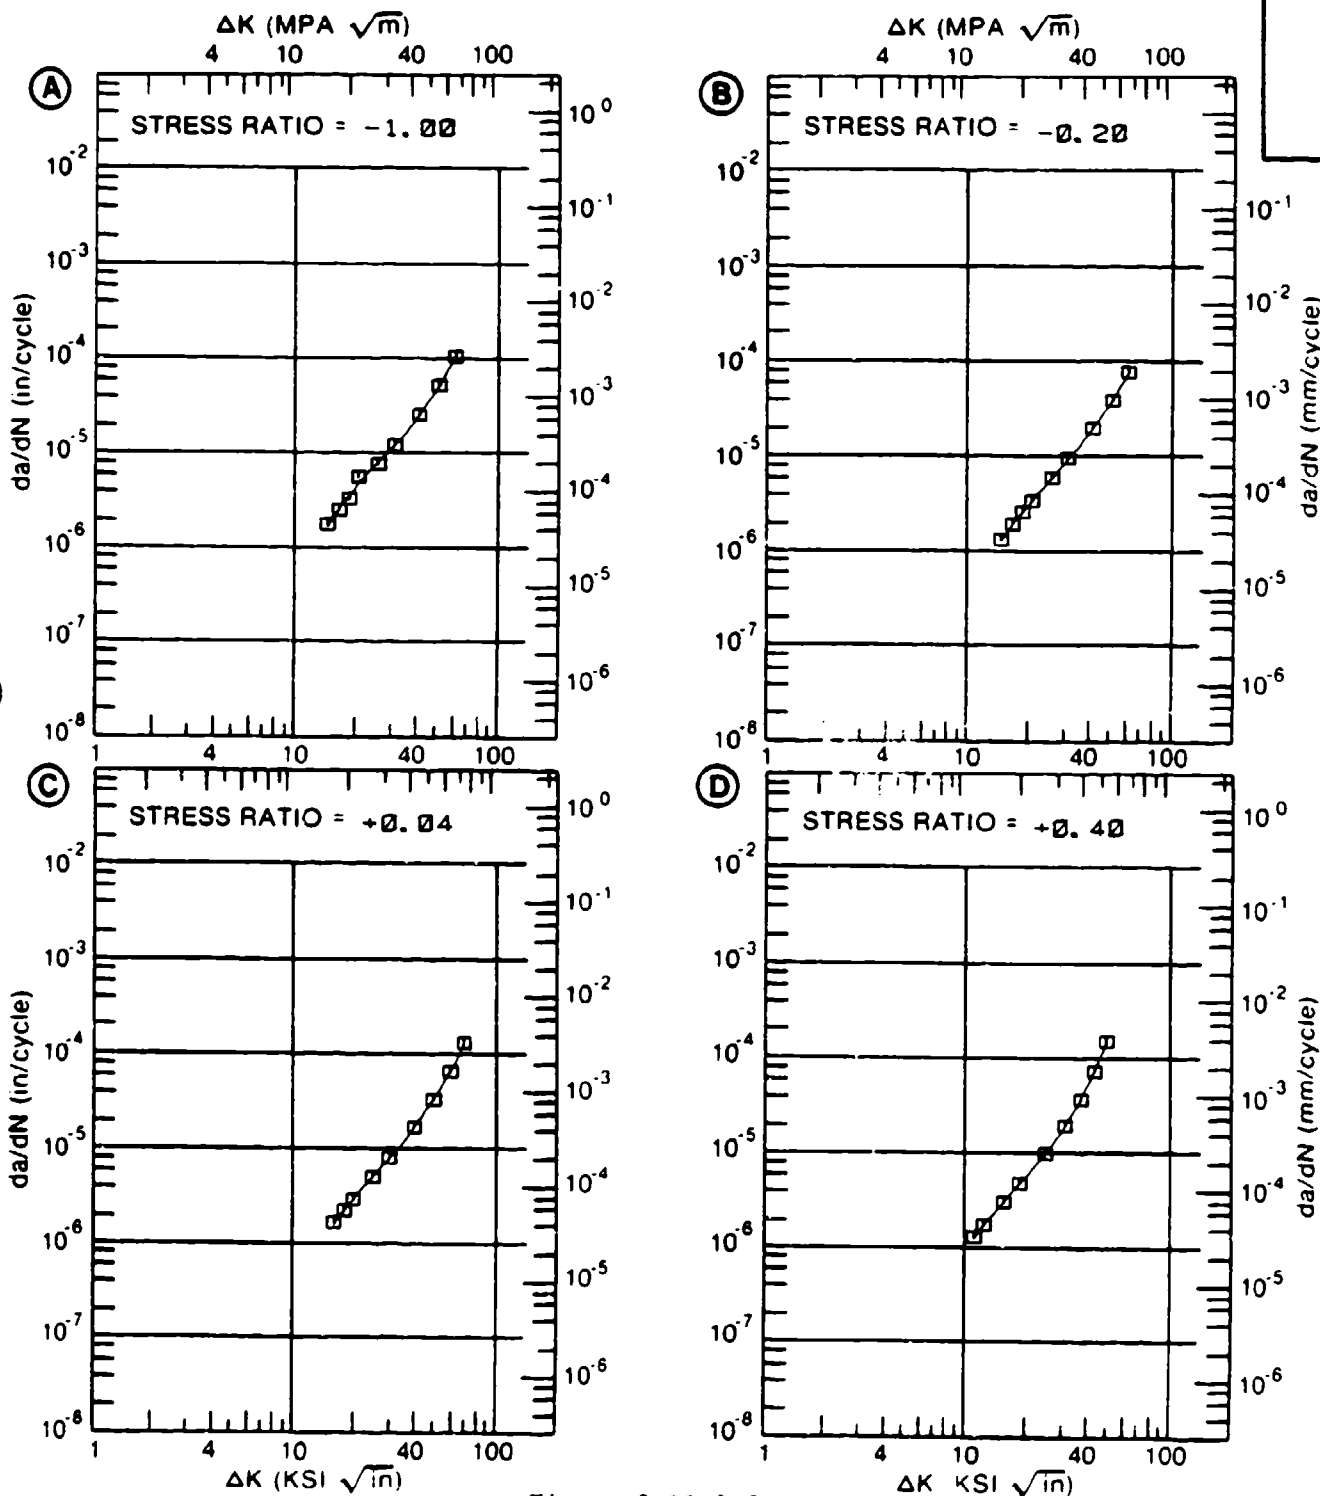


Figure 3.11.3.5

Table 3.11.3.6

CONDITION	--PRODUCT--		TEST SPEC	YIELD STR	ENVIRONMENT	---SPECIMEN---		CRACK LENGTH (IN)	K (ISCC)	K (ISCC) MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
	FORM	THICK (IN)				THICK (IN)	DESIGN (IN)						
H 900	B	2.25	R.T.	171.2	INDUSTRIAL ATH	2.000	1.000	CT	71.80	68.00		1973	866688
H 900	B	2.25	R.T.	171.2	SEACDAST ATH	2.000	1.000	CT	71.80	36.00		1973	866688
H 900	B	2.25	R.T.	171.2	20 PCT NAACL	2.000	1.000	CT	71.80	33.00		1973	866688
H1150M	B	2.25	R.T.	93.1	INDUSTRIAL ATH	2.000	1.000	CT	75.70	72.00*		1973	866688
H1150M	B	2.25	R.T.	93.1	SEACDAST ATH	2.000	1.000	CT	75.70	72.00*		1973	866688
H1150M	B	2.25	R.T.	93.1	20 PCT NAACL	2.000	1.000	CT	75.70	72.00*		1973	866688

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(KISCC/TYS)SQUARED

Table 3.12.3.1

CONDITION	-- PRODUCT FORM THICK (IN)	TEST SPEC TEMP (F)	DR STR (KSI)	ENVIRONMENT	WIDTH (IN)	SPECIMEN		CRACK LENGTH (IN)	K (KSI)	MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
						M	B						
H 900	F	3 00	R T	175 0 3 5 PCT NAACL	1.500	0.480	CANT	96.80	80.00*			> 60000	1971 84333
H1000	F	3 00	R T	157 9 3 5 PCT NAACL	1.500	0.480	CANT	114.00	114.00*			> 60000	1971 84333

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.3(KI/SC/TYS)SQUARED

Table 3.13.3.1

CONDITION	FORM	THICK (IN)	TEST TEMP (F)	OR STR (KSI)	SPEC YIELD ENVIRONMENT	WIDTH (IN)	SPECIMEN THICK (IN)	DESIGN (IN)	CRACK LENGTH (IN)	K (ISCC)	STAN DEV	TEST TIME (MIN)	DATE REFER					
														H	B	A		
H 900	F	4.50	R T	---	174.9	3.5	PCT NAACL	1.500	0.480	CANT	----	74.50	55	80	>	48000	1971	84333
H1000	F	4.50	R T	---	137.6	3.5	PCT NAACL	1.500	0.480	CANT	----	120.00	120	00*	>	60000	1971	84333

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(KISCC/TYS)SQUARED

Table 3.14.1.1

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL 17-4PH

TEST CONDITIONS

SPECIMEN ORIENTATION T :

ENVIRONMENT: LAB AIR AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))					FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)				
				2	3	5	10	20	50	100			
H1023	ROUND BAR	0.10	30.00				0.06	2.00					
H1025	ROUND BAR	0.50	10.00					5.77					
H1023	ROUND BAR	0.50	30.00				0.03	0.51					

Table 3.14.2.1

CONDITION	STAINLESS SIFFL 17-4PH		K(IIC)	YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	THICK (IN)	TEMP (F)	W	THICK (IN)	DESIGN	CRACK LENGTH (IN)	K(IIC)/IYS**2	K(IIC) MEAN (KSI) SQRT IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)														
M 975	RR	3.25	R.T.	168.0	L-R	1.000	2.000	1.000	NB	1.000	0.63	94.60			84212	
HIC25	BR	3.00	R.T.	175.3	1-1	1.990	0.503	0.937	CT	0.937	0.45	74.50			1979 DA001	

TABLE 3.14.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.14.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 17-4PH
CONDITION: H900
ENVIRONMENT: R.T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.08			
DELTA K MIN	A: 7.54	.126			
	B:				
	C:				
	D:				
	8.00	.150			
	9.00	.217			
	10.00	.305			
	13.00	.745			
	16.00	1.54			
	20.00	3.38			
25.00	7.25				
30.00	13.1				
35.00	20.9				
40.00	30.5				
50.00	53.1				
DELTA K MAX	A: 56.40	68.4			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 22.74
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: H900
 FORM: 0.56" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 170.5 KSI
 ULT. STRENGTH: 192.7 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 1.969"
 REFERENCES: DA001

STAIN.
 STEEL

17-4PH

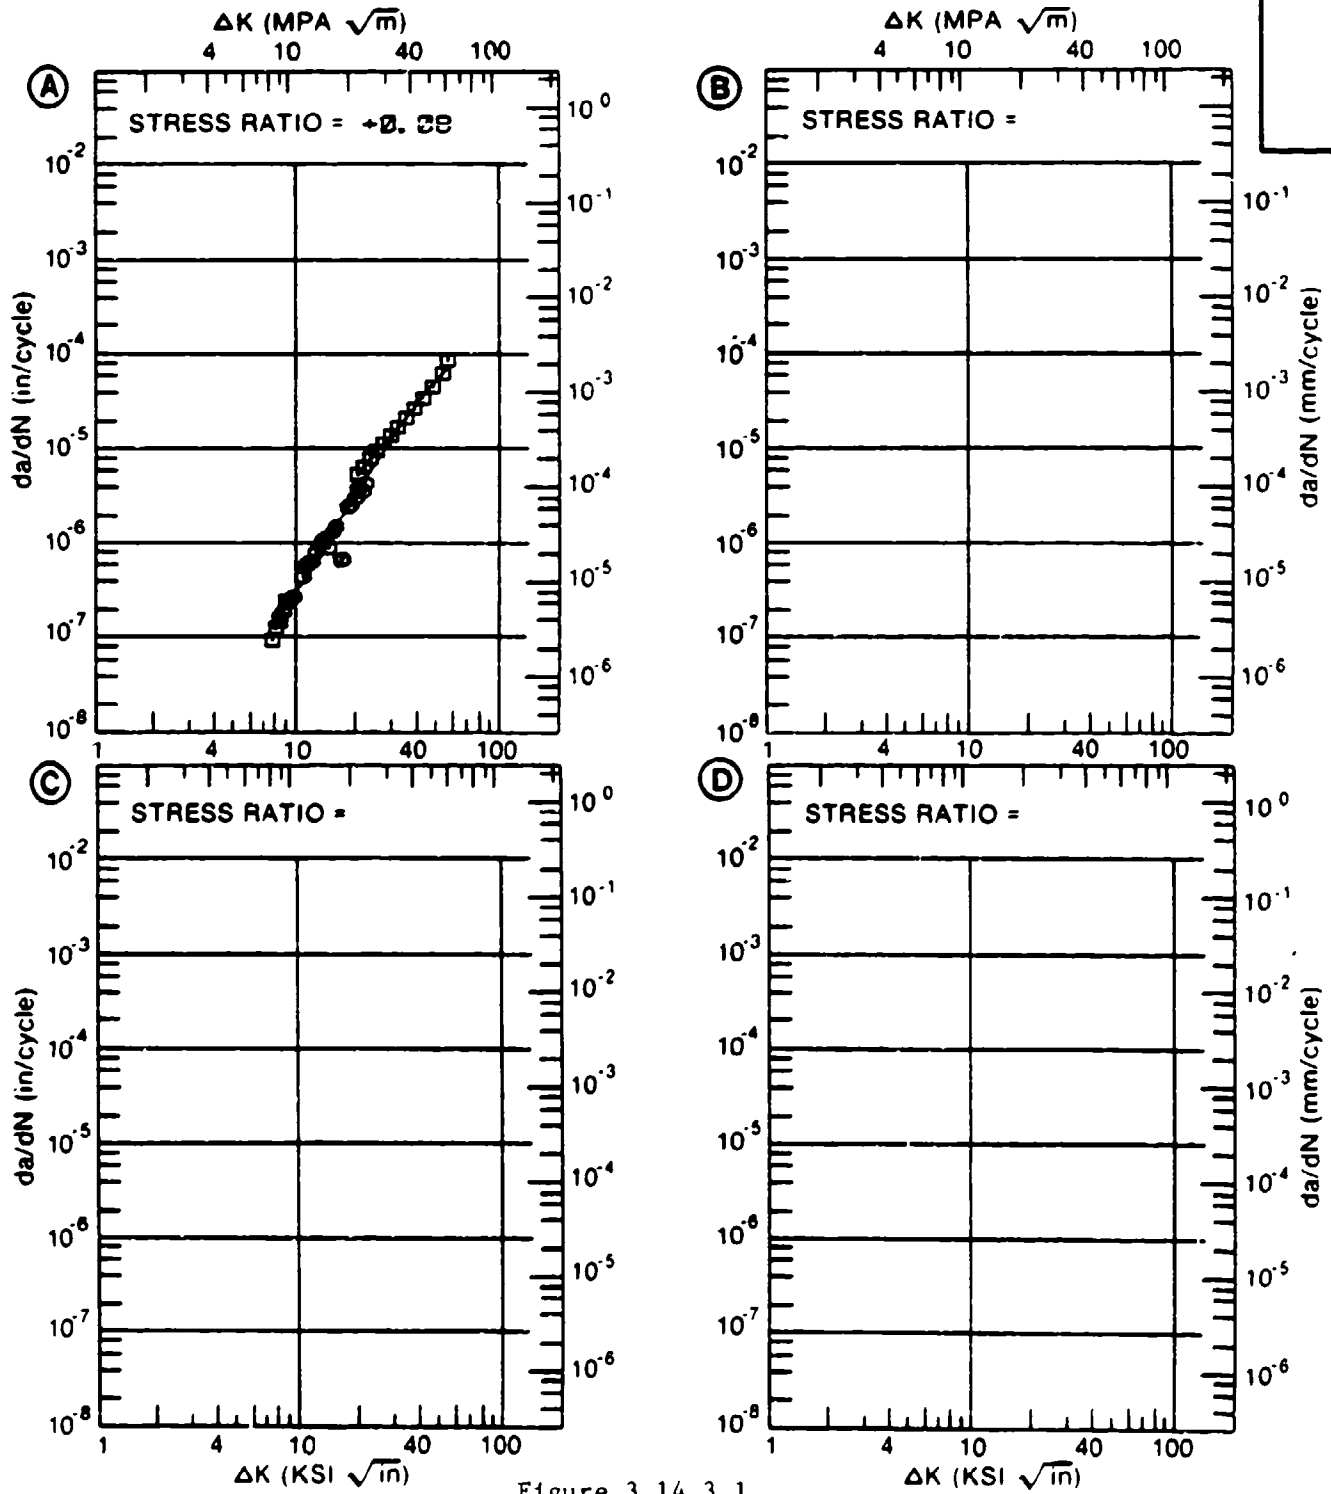


Figure 3.14.3.1

TABLE 3.14.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 3.14.3.2 INDICATING EFFECT
OF ENVIRONMENTMATERIAL: STAINLESS STEEL 17-4PH
CONDITION: H1025

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E= R. T. H. H. A.			
DELTA K MIN	A: 8.33	.214		
	9.00	.245		
	10.00	.330		
	13.00	.945		
	16.00	2.15		
	20.00	3.51		
DELTA K MAX	A: 20.04	3.51		
	B:			
	C:			
	D:			

ROOT MEAN SQUARE 17.98
PERCENT ERRORLIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: H1025
 FORM: Ø. 13" TH CASTING
 SPECIMEN TYPE: CCP
 ORIENTATION:
 STRESS RATIO: +0.02
 FREQUENCY: 1.0 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: Ø. 103- Ø. 113"
 SPECIMEN WIDTH: 2.915- 2.955"
 REFERENCES: GD010

STAIN.
 STEEL

17-4PH

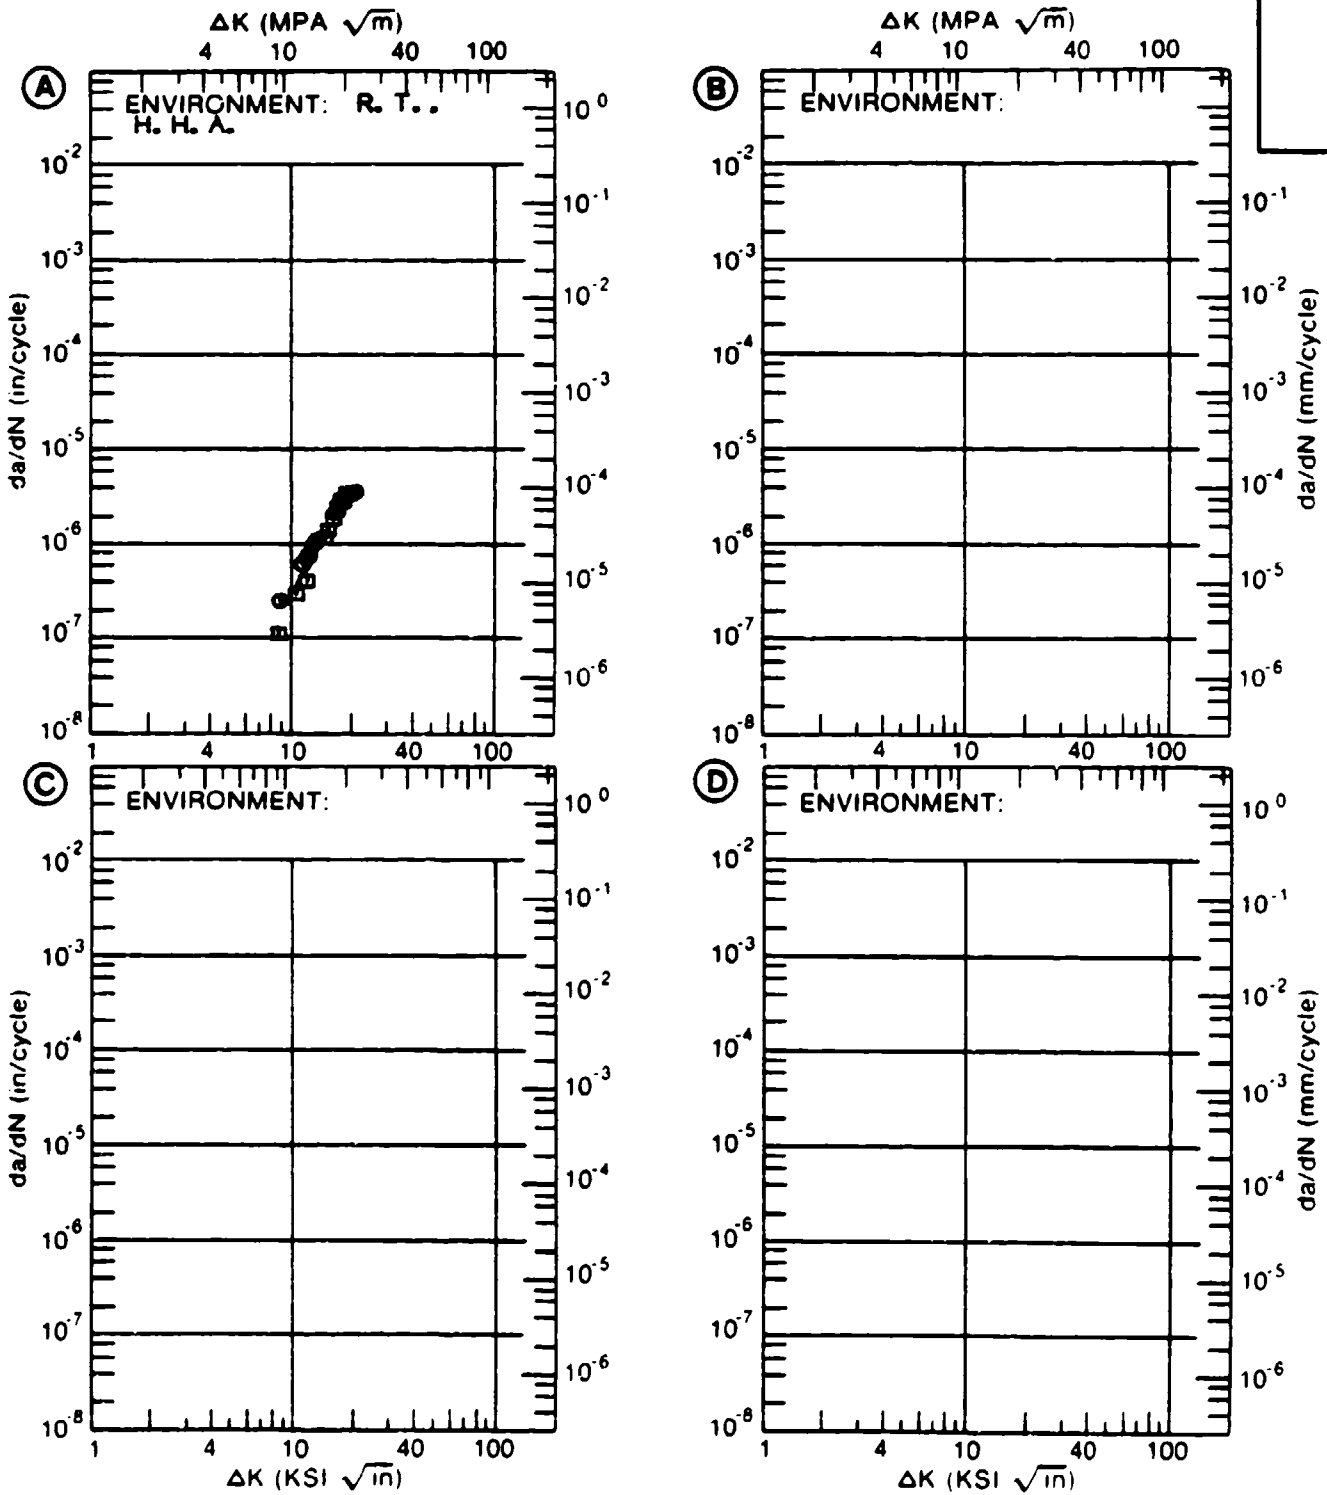


Figure 3.14.3.2

TABLE 3.14.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.14.3.3 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 17-4PH					
CONDITION: H1025					
ENVIRONMENT: R.T., LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K	A: 20.54	1.48			
MIN	B: 11.39		.708		
	C:				
	D:				
	13.00		1.33		
	16.00		2.76		
	20.00		5.77		
	25.00	3.15	16.5		
	30.00	5.61			
	35.00	9.33			
	40.00	15.9			
DELTA K	A: 49.82	54.3			
MAX	B: 28.37		39.5		
	C:				
	D:				
ROOT MEAN SQUARE		8.26	7.53		
PERCENT ERROR					
LIFE	0.0-0.3				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: H1025
 FORM: 3.0" TH ROUND BAR
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 10.0 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 175.3 KSI
 ULT. STRENGTH: 179.8 KSI
 SPECIMEN THK: 0.50"
 SPECIMEN WIDTH: 1.99- 2.00"
 REFERENCES: DA001

STAIN.
 STEEL

17-4PH

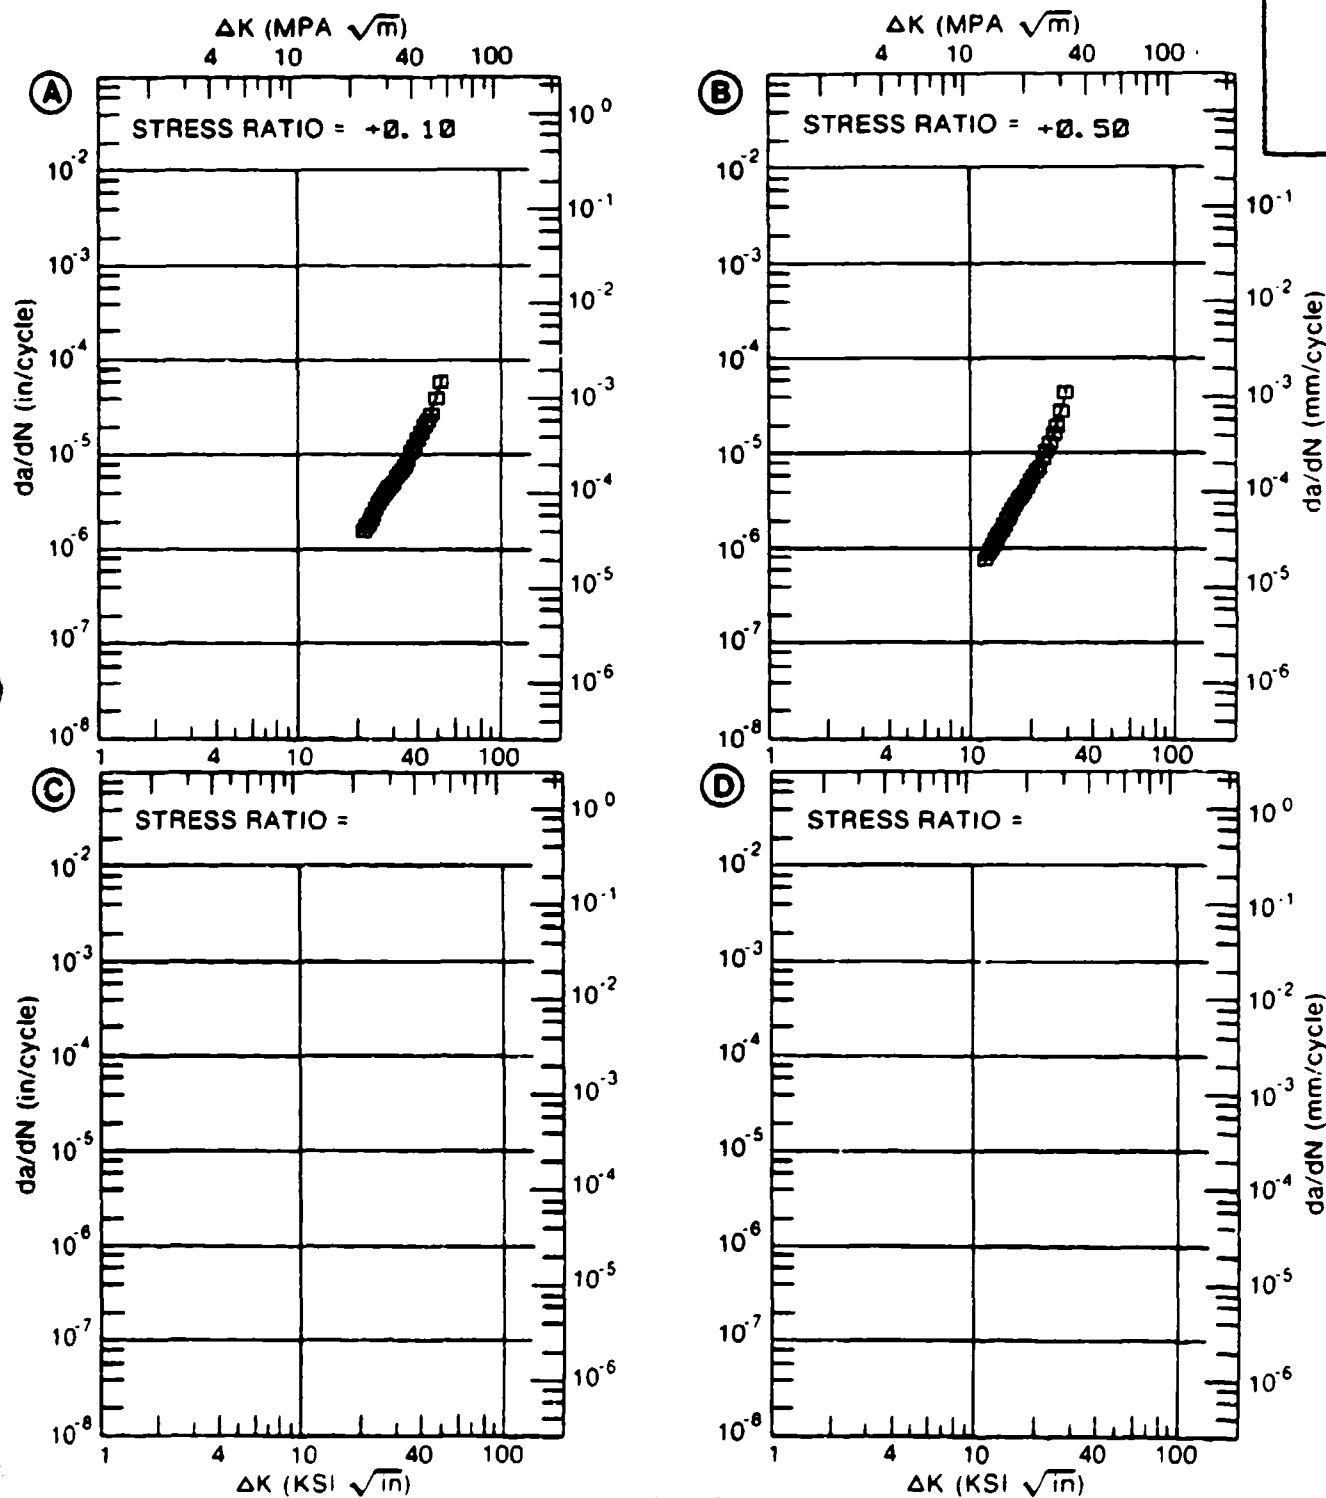


Figure 3.14.3.3

TABLE 3.14.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.14.3.4 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 17-4PH
CONDITION: H1025
ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K	A: 7.48	.0111			
MIN	B: 4.00		.00984		
	C:				
	D:				
	5.00		.0357		
	6.00		.0802		
	7.00		.143		
	8.00	.0175	.229		
	9.00	.0344	.347		
	10.00	.0607	.512		
	13.00	.288			
	16.00	.899			
	20.00	2.00			
	25.00	3.66			
	30.00	7.22			
	35.00	13.7			
DELTA K	A: 38.39	19.6			
MAX	B: 12.62		1.41		
	C:				
	D:				
ROOT MEAN SQUARE		11.17	6.89		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: H1025
 FORM: 3.0" TH ROUND BAR
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 30.0 HZ
 ENVIRONMENT: R.T., LAB AIR

YIELD STRENGTH: 175.3 KSI
 ULT. STRENGTH: 179.8 KSI
 SPECIMEN THK: 0.25"
 SPECIMEN WIDTH: 1.99- 2.00"
 REFERENCES: DA001

STAIN.
 STEEL

17-4PH

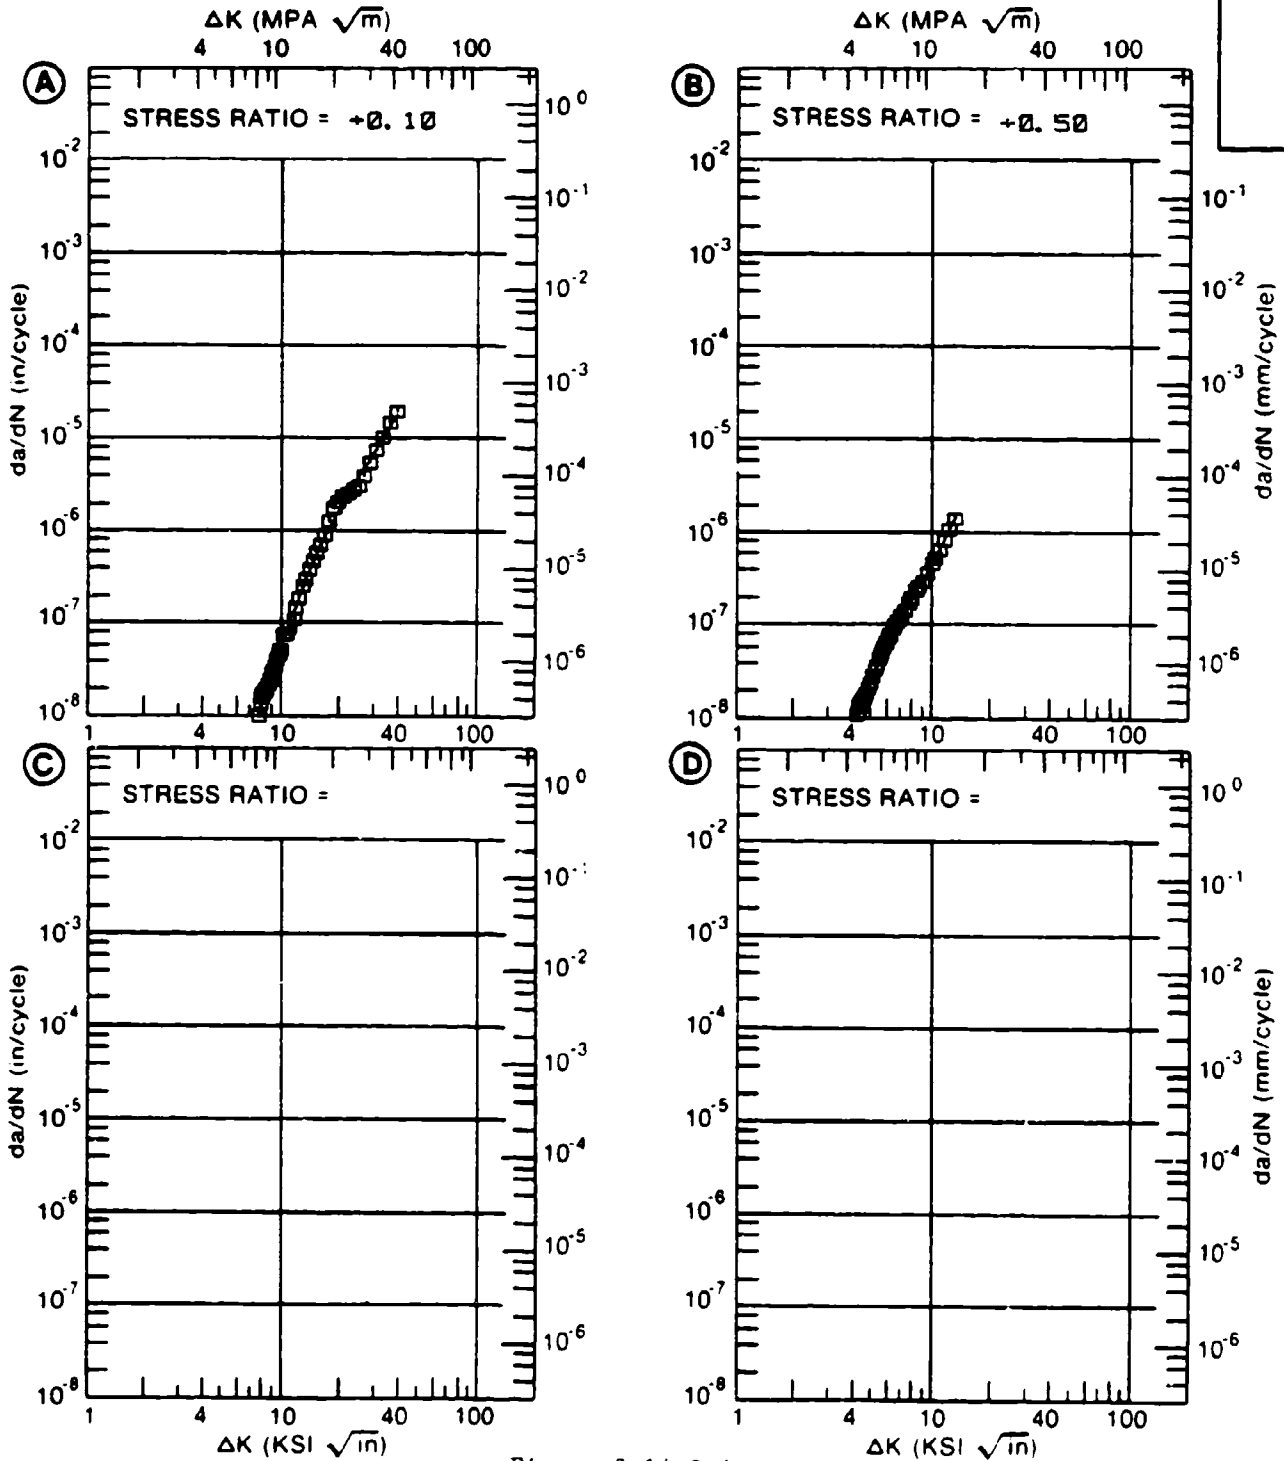


Figure 3.14.3.4

Table 3.14.3.5

CONDITION	STAINLESS STEEL 17-4PH										K (ISCC)											
	FORM	THICK (IN)	TEMP (F)	TEST SPEC OR STR	YIELD STRENGTH (KSI)	ENVIRONMENT		SPECIMEN		CRACK LENGTH (IN)		K (ISCC)										
						SIP	3.5 PCT NaCl	WIDTH (IN)	THICK (IN)				DESIGN (IN)	LENGTH (IN)								
H 500	D	1.75	R.T.	---	176	5	3.5	PCT NaCl	1.500	0	480	CANT	---	51	50	51	50	MEAN	DEV	STAN	TEST TIME (MIN)	DATE REFER
H1000	B	1.75	R.T.	---	157	9	3.5	PCT NaCl	1.500	0	480	CANT	---	119	00	119	00*	119	00*	---	> 60000	1971 84333

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5 (KISCC/TYS) SQUARED

Table 3.15.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
STAINLESS STEEL ALLOY 17-7PH AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION	(NUMBER OF SPECIMENS)
		ROLLED BAR
CONDITION/HT	L-I	L-I
RM1050	-----	47.0 ± 0.7 (3)

Table 3.15.2.1

CONDITION	STAINLESS STEEL 17-7PH K(IIC)													
	---PRODUCT--- FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.9* K(IIC)/TYS)**2 (IN)	K(IIC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
						M	B	A						
RH1050	RB	1.25	R.T.	T-L	190.0	2.000	1.000	CT	1.066	0.15	46.30		1973	86688
		1.25			190.0	2.000	1.000	CT	1.025	0.15	47.70		1973	86688
		1.25			190.0	2.000	1.000	CT	1.026	0.15	47.10	47.0/	0.7	1973

TABLE 3.15.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 3.15.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 17-7PH
 CONDITION: TH1050
 ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A:	2.85	.00325		
	B:				
	C:				
	D:				
		3.00	.00435		
		3.50	.00947		
		4.00	.0155		
		5.00	.0252		
		6.00	.0425		
		7.00	.0857		
DELTA K MAX		8.00	.152		
		9.00	.276		
		10.00	.433		
		13.00	1.19		
		16.00	2.38		
	A:	18.70	3.75		
	B:				
C:					
D:					
ROOT MEAN SQUARE		11.25			
PERCENT ERROR					
LIFE	0.0-0.3				
PREDICTION	0.5-0.8		1		
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: TH1050
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 20.0 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 194.0 KSI
 ULT STRENGTH: 208.1 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 1.000"
 REFERENCES: DA001

STAIN.
STEEL

17-7PH

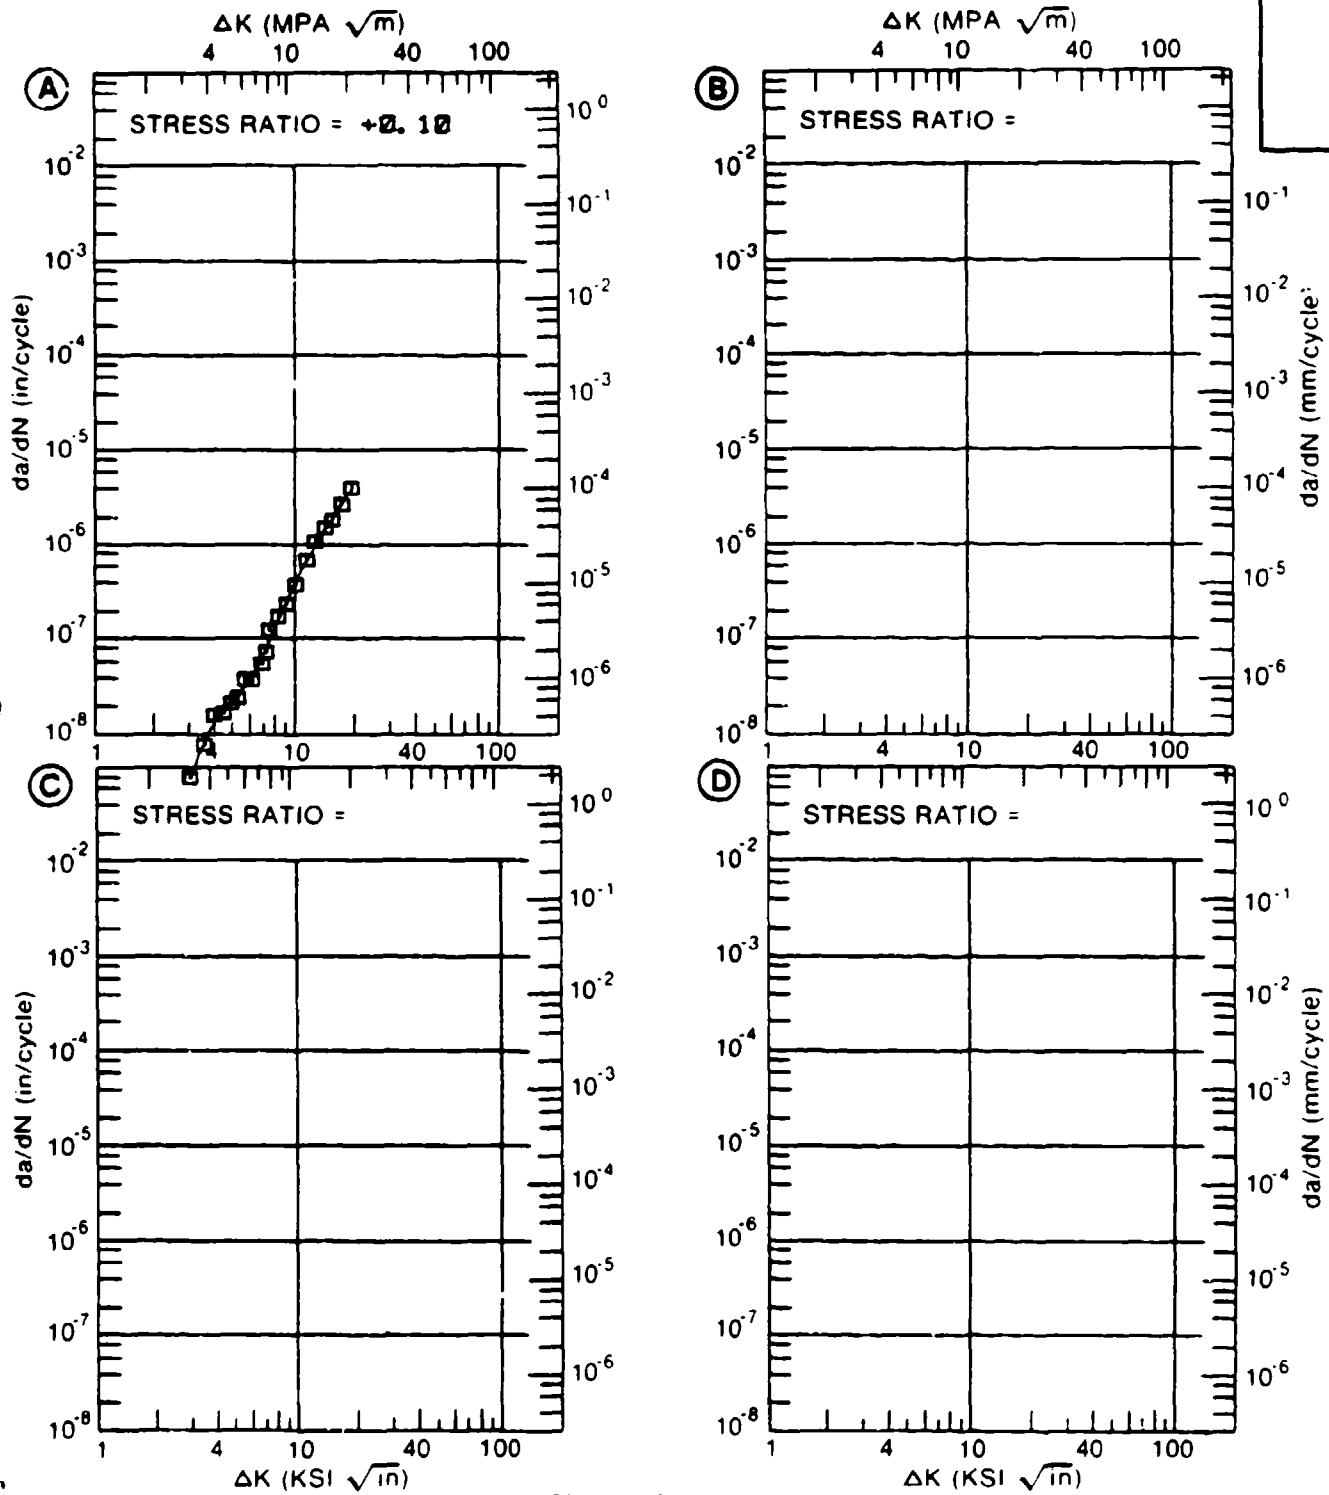


Figure 3.15.3.1

TABLE 3.15.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.15.3.2 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 17-7PH
CONDITION: TH1050
ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K	A: 3.82	.00558			
MIN	B:				
	C:				
	D:				
	4.00	.00944			
	5.00	.0264			
	6.00	.0447			
	7.00	.0841			
	8.00	.153			
	9.00	.253			
	10.00	.388			
	13.00	1.03			
	16.00	2.12			
	20.00	4.44			
	25.00	9.34			
	30.00	17.5			
	35.00	30.7			
	40.00	51.4			
DELTA K	A: 49.65	205.			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 11.14
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8 1
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: TH1050
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 20.0 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 190.3 KSI
 ULT. STRENGTH: 203.3 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 1.989"
 REFERENCES: DA001

STAIN.
STEEL

17-7PH

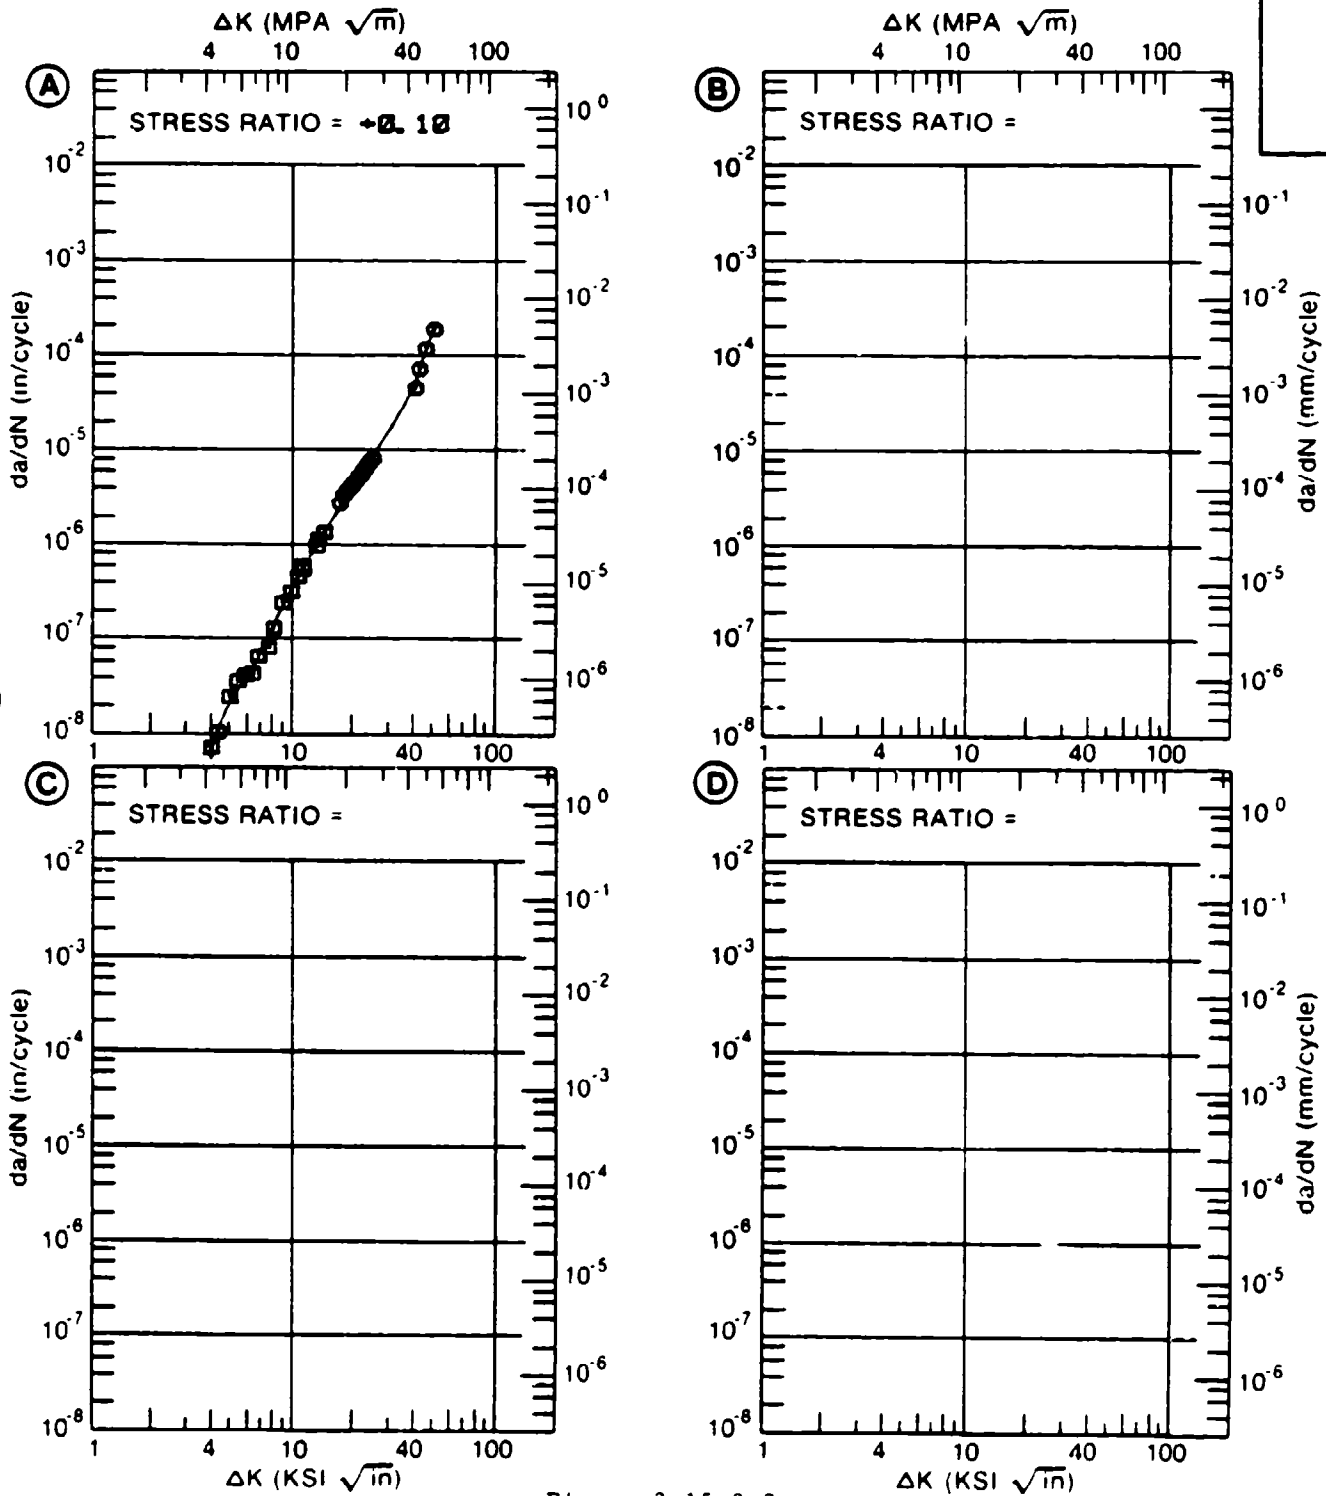


Figure 3.15.3.2

Table 3.15.3.3

CONDITION	PROJECT		TEST SPEC		YIELD (KSI)	ENVIRONMENT	SPECIMEN		CRACK LENGTH (IN)	K (KSI)	K (SC)	MEAN (IN)	DEV	TEST TIME (MIN)	DATE	REFER
	FORM	THICK (IN)	TEMP (F)	OR			STR	WIDTH (IN)								
RH 970	B	1.5	R T	---	171.3	3.3	5 PCT NAACL	1.500	0.480	CANT	---	32.30	19.00	> 42000	1971	84333
RH1050	B	1.25	R T	T-L	190.5	INDUSTRIAL	ATM	2.000	1.000	CT	---	47.00	24.00	---	1973	86688
RH1050	B	1.25	R T	T-L	190.5	SEACOAST	ATM	2.000	1.000	CT	---	47.00	12.00	---	1973	86688
RH1050	B	1.25	R T	T-L	190.5	20 PCT	NAACL	2.000	1.000	CT	---	47.00	10.00	---	1973	86688
TH1050	B	1.75	R T	---	---	3.5	PCT NAACL	1.500	0.480	CANT	---	38.70	15.80	> 30000	1971	84333

Table 3.16.1.1.1

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL 304

TEST CONDITIONS

SPECIMEN ORIENTATION Unknown

ENVIRONMENT: LAB AIR AT R.T.

CONDITION/MT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
ANNEALED	SHEET	0.05	10.00				0.16	3.07		
ANNEALED	SHEET	0.05	15.00				0.13	2.83		
ANNEALED	SHEET	0.10	1.67					2.86		
ANNEALED	SHEET	0.10	6.00					2.56		
ANNEALED & AGE	PLATE	0.05	3.00						1.38	

Table 3.16.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

STAINLESS STEEL 304

TEST CONDITIONS

SPECIMEN ORIENTATION: L-T

ENVIRONMENT: LAB AIR AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K (LEVELS (KSI SQRT(IN)))	2.5	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
ANNEALED	PLATE	0.00	0.03								36.0
ANNEALED	PLATE	0.00	6.67						1.92	28.5	

TABLE 3.16.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.16.3.1 INDICATING EFFECT

OF FREQUENCY

MATERIAL: STAINLESS STEEL 304
CONDITION: ANNEALED
ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		F(HZ)= 10.0	F(HZ)= 15.0		
DELTA K MIN	A: 9.98	.160			
	B: 9.16		.112		
	C:				
	D:				
		10.00	.163	.133	
	13.00	.438	.360		
	16.00	1.37	1.01		
	20.00	3.07	2.83		
DELTA K MAX	A: 23.49	6.30			
	B: 21.04		3.45		
	C:				
	D:				
ROOT MEAN SQUARE		15.06	26.43		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.23	3	3		
SUMMARY	1.25-2.0		1		
(NP/NA)	>2.0				

CONDITION/HT: ANNEALED
 FORM: SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION:
 STRESS RATIO: +0.05
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.010"
 SPECIMEN WIDTH: 0.995- 1.000"
 REFERENCES: HD000

STAIN.
 STEEL

304

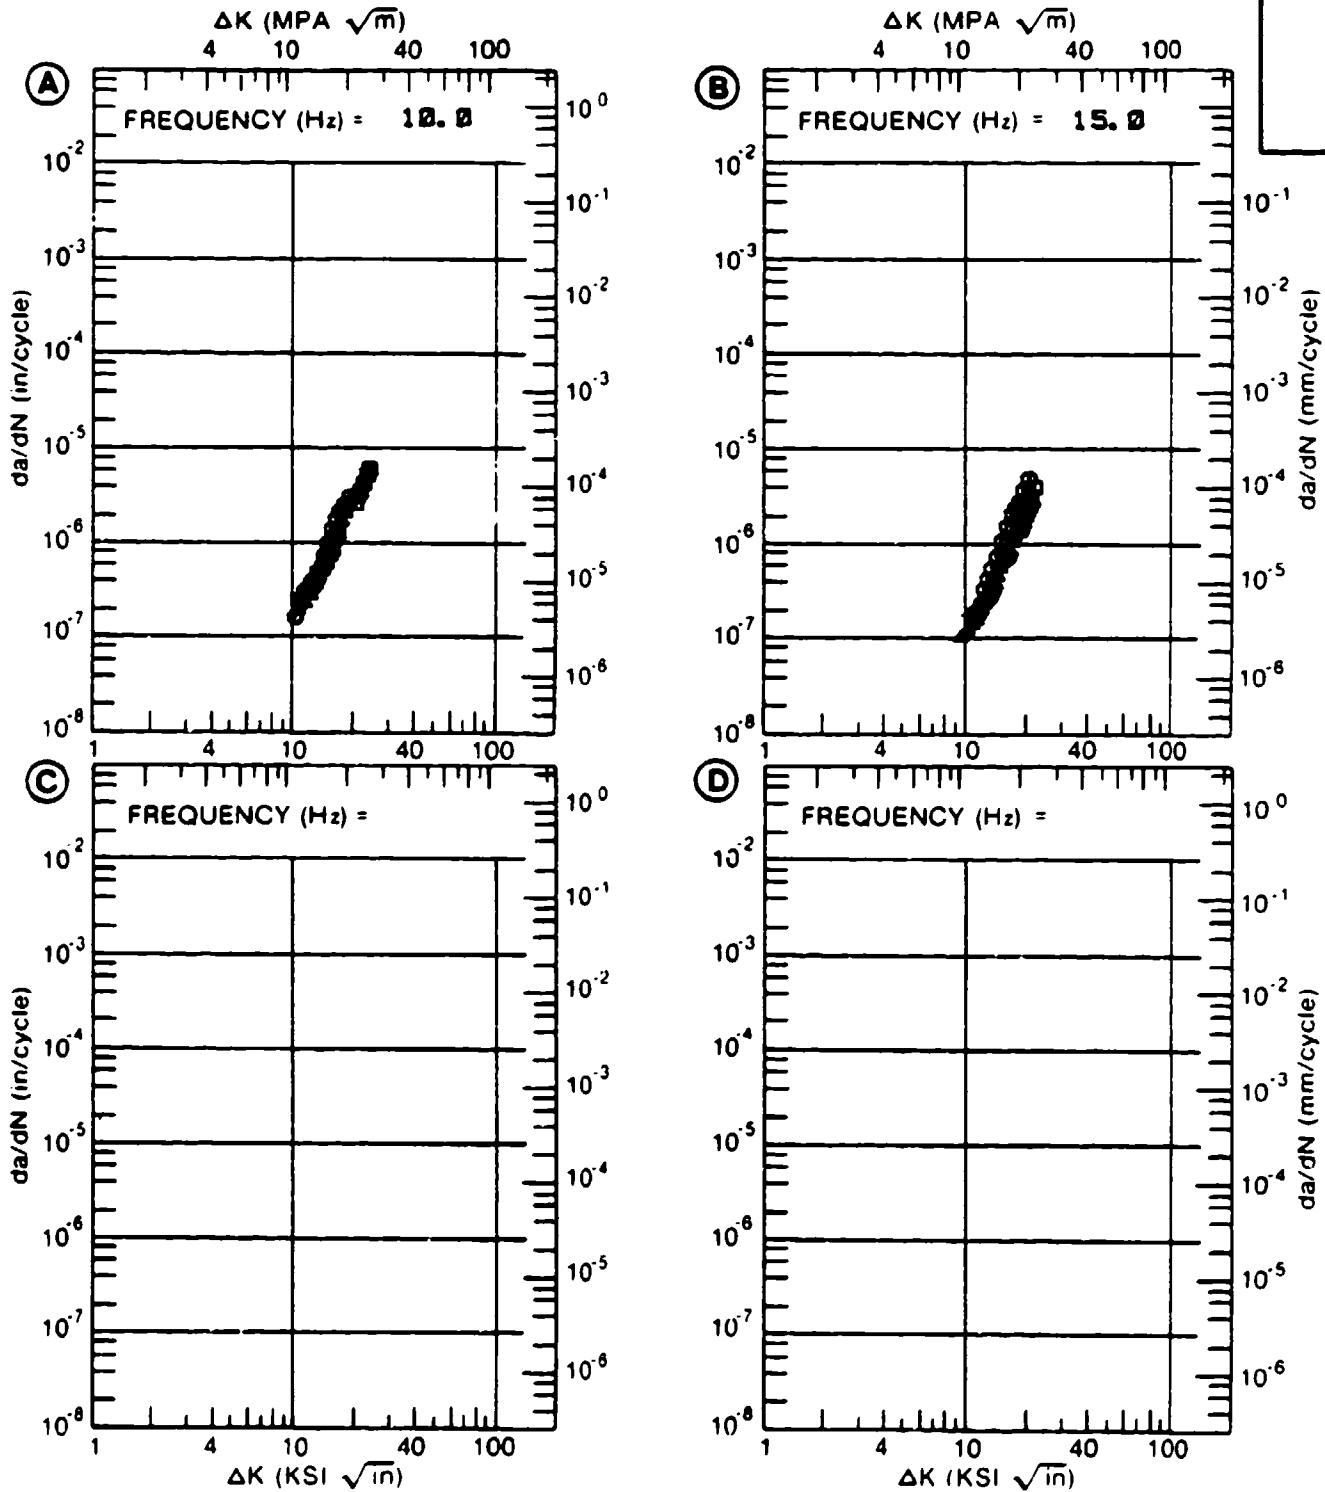


Figure 3.16.3.1

TABLE 3.16.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.16.3.2 INDICATING EFFECT

OF FREQUENCY

MATERIAL: STAINLESS STEEL 304
CONDITION: ANNEALED
ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	F(HZ)= 1.67		F(HZ)= 6.00	
DELTA K MIN	A: 14.71	.772	B: 10.85	.128
	C: 13.00		D: 16.00	.312
	16.00	1.19	20.00	.657
	20.00	2.86	25.00	2.56
	25.00	4.61	30.00	10.6
DELTA K MAX	A: 32.52	20.3	B: 21.51	4.77
	C:		D:	
ROOT MEAN SQUARE PERCENT ERROR	23.51	8.28		
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5	2	0.5-0.8	2
	0.8-1.25	2	1.25-2.0	1
	>2.0			

CONDITION/HT: ANNEALED
 FORM: SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION:
 STRESS RATIO: +0.10
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.010"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: HD000

STAIN.
 STEEL

304

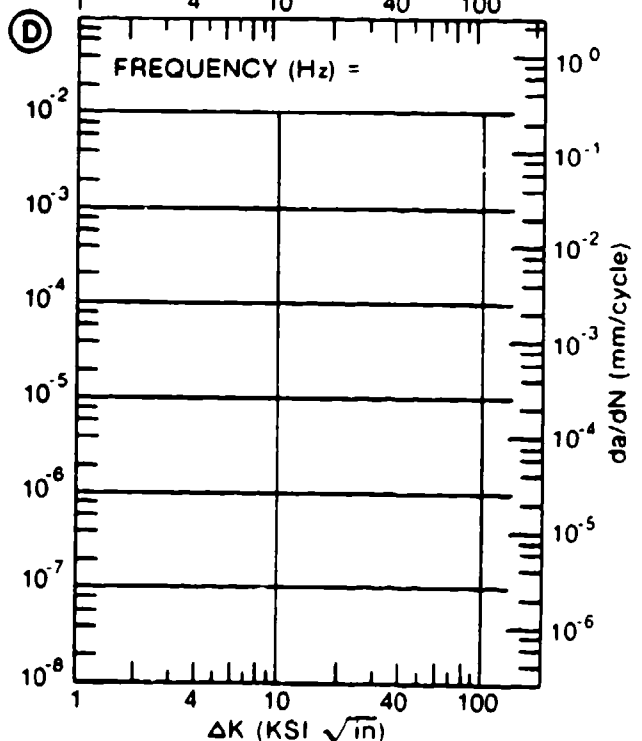
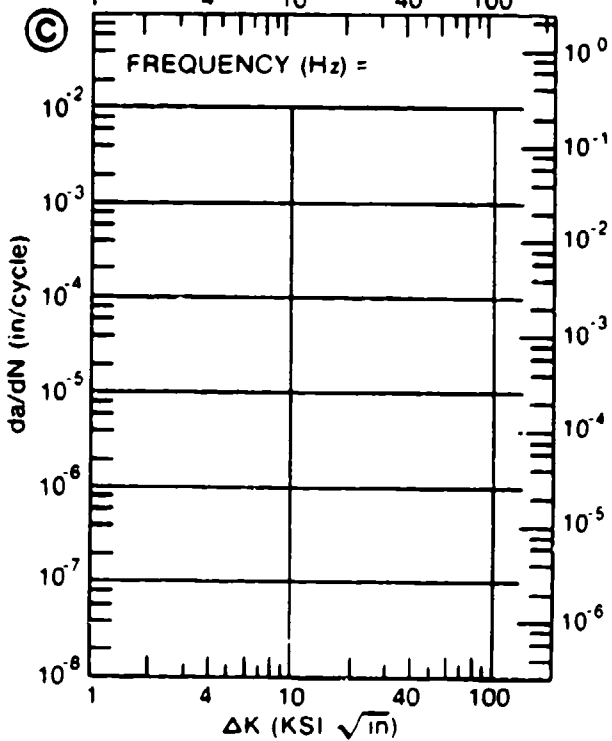
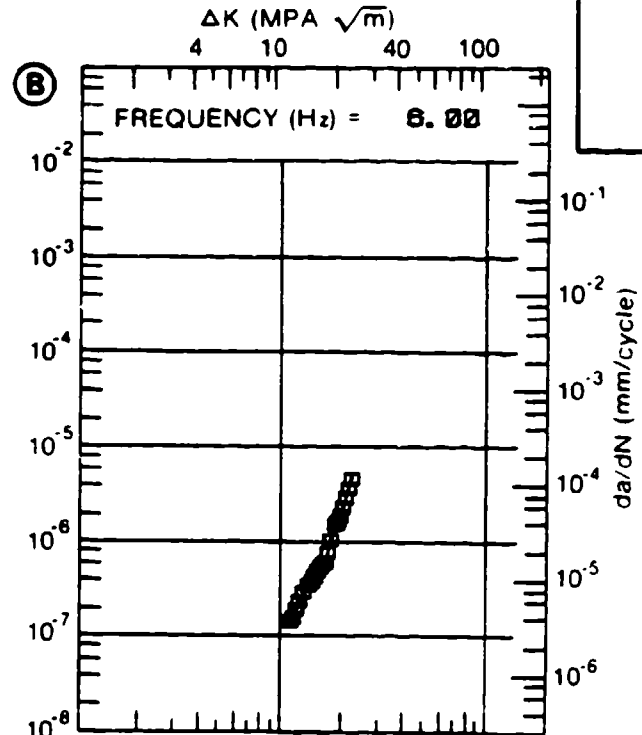
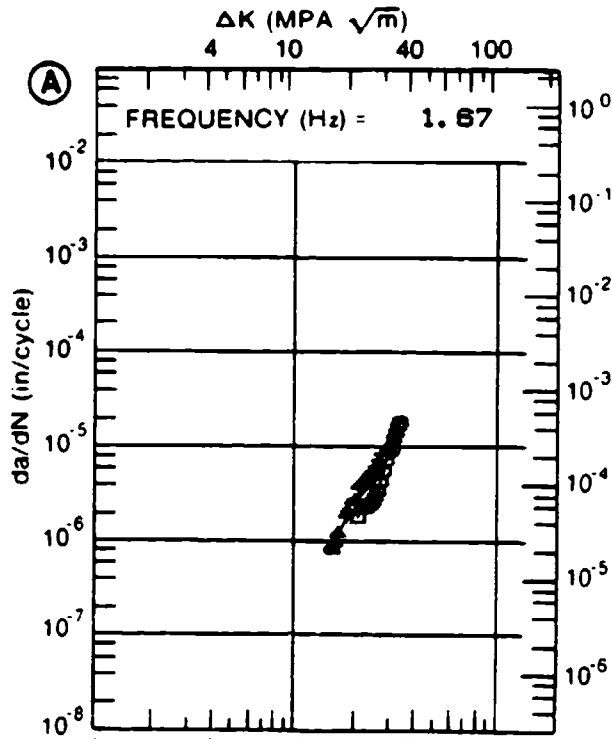


Figure 3.16.3.2

TABLE 3.16.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.16.3.3 INDICATING EFFECT
OF FREQUENCY

MATERIAL: STAINLESS STEEL 304
CONDITION: ANNEALED
ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		F(HZ)= 0.03		F(HZ)= 6.67	
DELTA K MIN	A: 32.53	11.1		854	
	B: 16.50				
	C:				
	D:				
	20.00		1.92		
	25.00		3.05		
	30.00		4.50		
	35.00	14.7	8.12		
	40.00	24.7	15.3		
	50.00	56.0	28.5		
	60.00	101.	45.7		
	70.00	154.			
	80.00	205.			
DELTA K MAX	A: 82.69	217.		78.3	
	B: 69.22				
	C:				
	D:				
ROOT MEAN SQUARE		5.23		5.67	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0		1	1	

CONDITION/HT: ANNEALED
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: SENT
 ORIENTATION: L-T
 STRESS RATIO: +0.00
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 39.6 KSI
 ULT. STRENGTH: 77.1 KSI
 SPECIMEN THK: 0.491"
 SPECIMEN WIDTH: 4.910- 4.950"
 REFERENCES: HD007

STAIN. STEEL
304

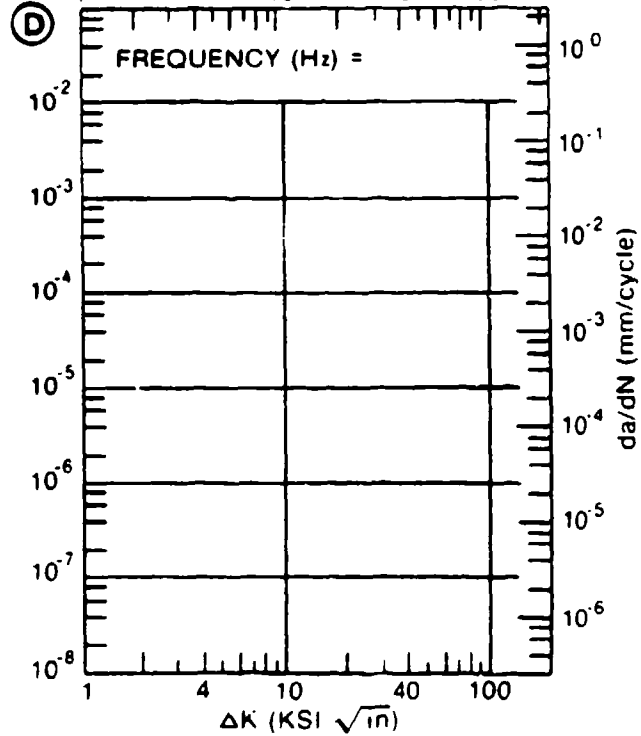
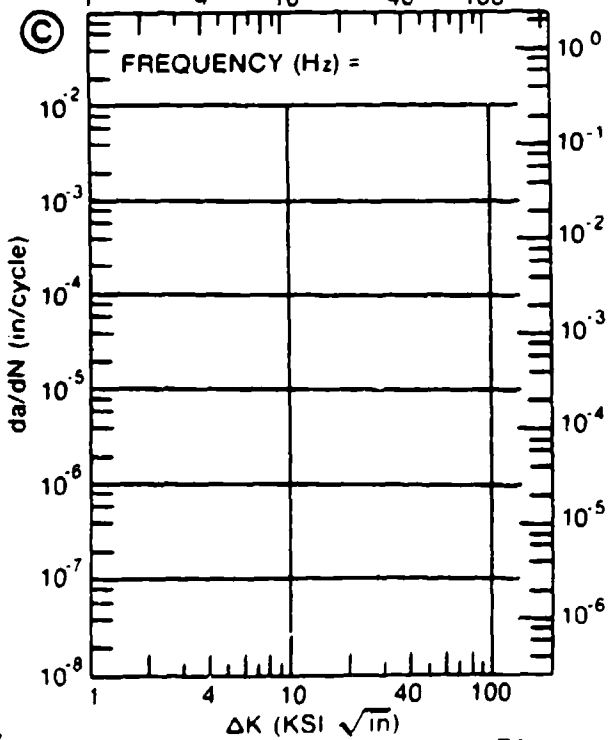
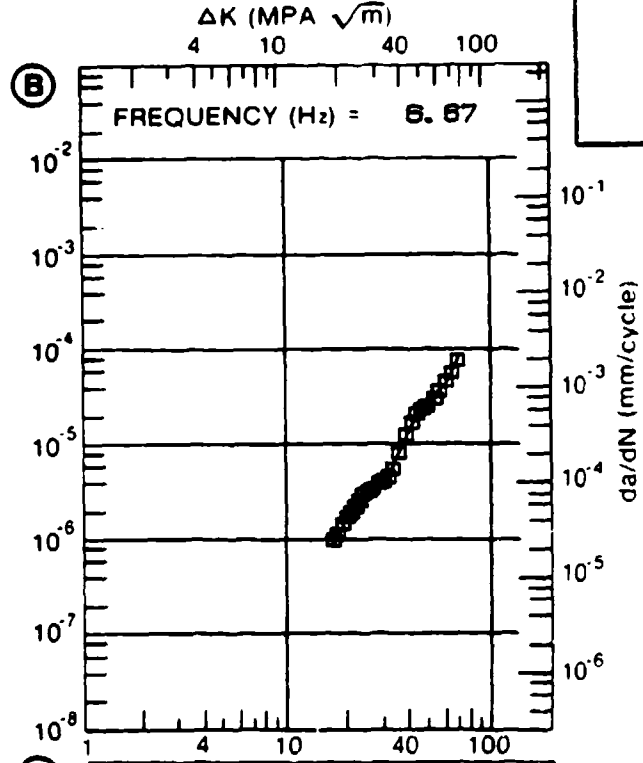
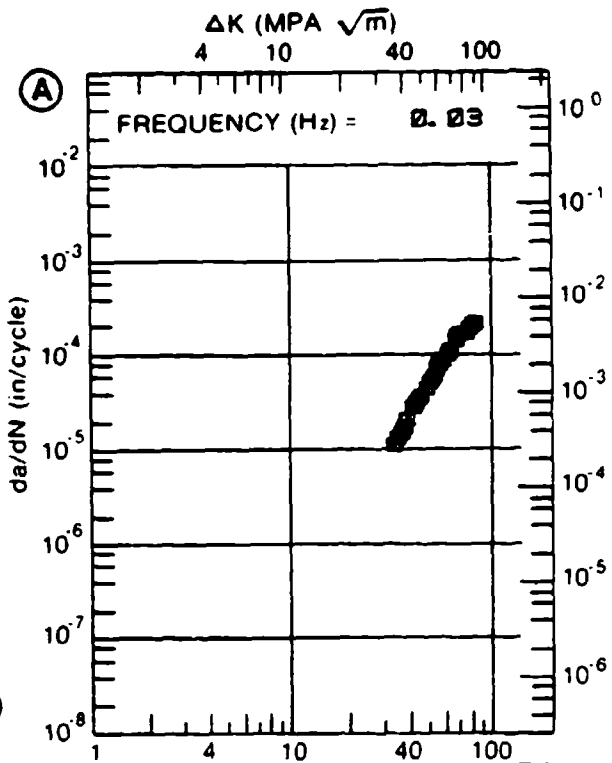


Figure 3.16.3.3

TABLE 3.16.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.16.3.4 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 304
CONDITION: ANNEALED
ENVIRONMENT: R.T., LAB AIR

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	R=+0.05			
DELTA K A:				
MIN B:				
C:				
D:				
200.00				
DELTA K A:				
MAX B:				
C:				
D:				

ROOT MEAN SQUARE 0.00
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: ANNEALED
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: VOL
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 39.6 KSI
 ULT. STRENGTH: 77.1 KSI
 SPECIMEN THK: 0.494"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: HD007

STAIN.
 STEEL

304

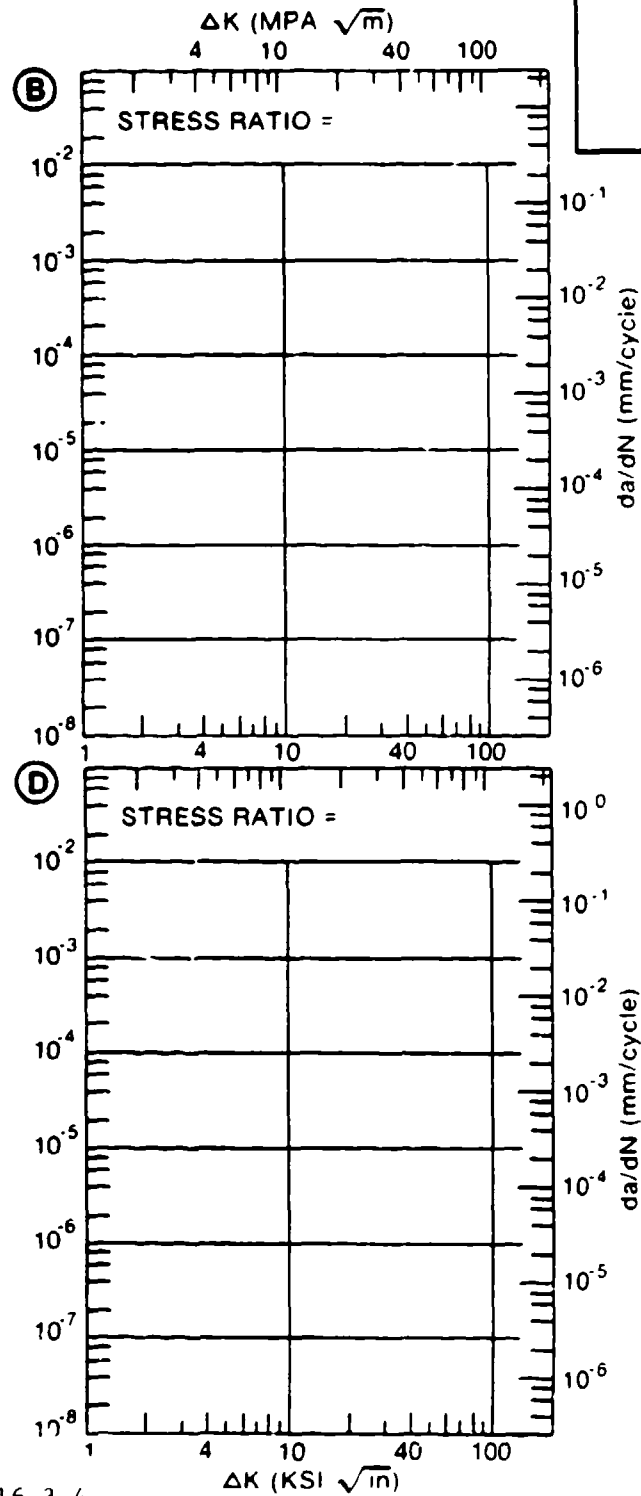
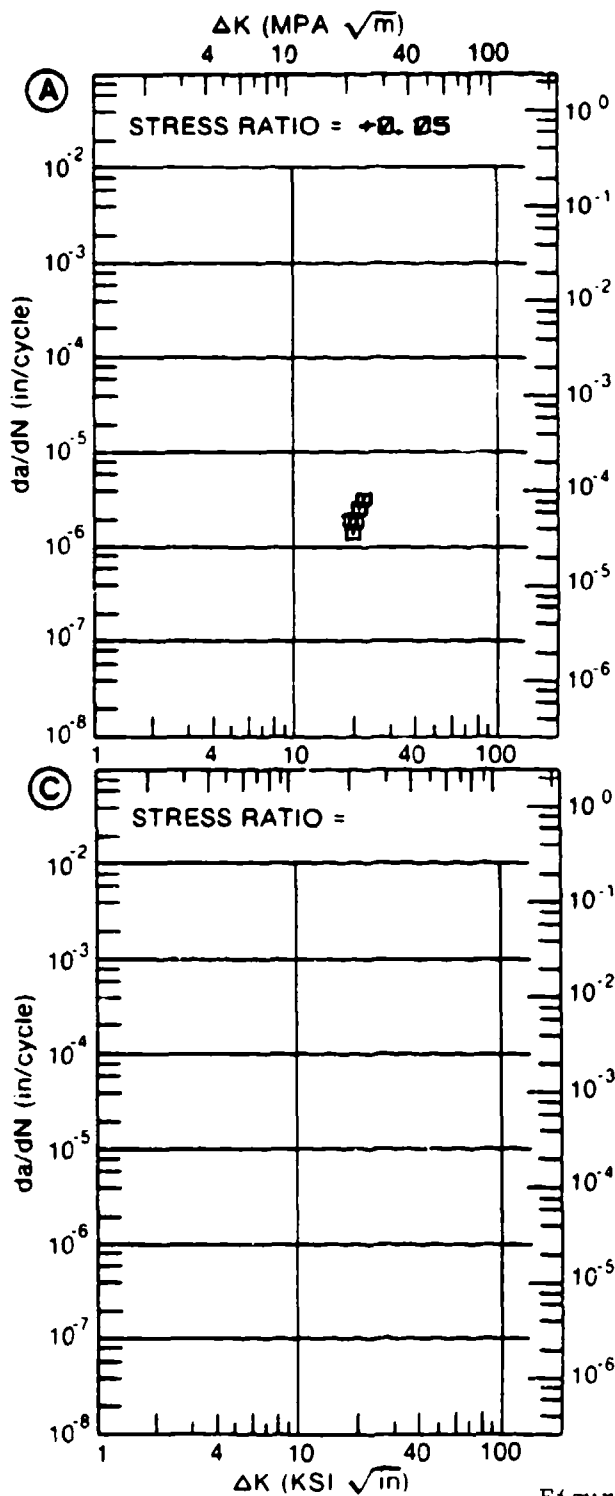


Figure 3.16.3.4

TABLE 3.16.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.16.3.5 INDICATING EFFECT
OF FREQUENCY

MATERIAL: STAINLESS STEEL 304
CONDITION: ANNEALED
ENVIRONMENT: R.T., LAB AIR

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	F(HZ)= 3.00	F(HZ)= 6.67		
DELTA K MIN	A: B: 16.13 C: D:	1.09		
	20.00	1.86		
	25.00	3.44		
	30.00	5.93		
	35.00	9.64		
	40.00	15.0		
	50.00	32.5		
	60.00	63.2		
DELTA K MAX	A: B: 67.92 C: D:	101.		
ROOT MEAN SQUARE PERCENT ERROR	0.00	5.89		
LIFE	0.0-0.5			
PREDICTION	0.5-0.8			
RATIO	0.8-1.25	1		
SUMMARY (NP/NA)	1.25-2.0 >2.0			

CONDITION/HT: ANNEALED
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: SENT
 ORIENTATION: T-L
 STRESS RATIO: +0.00
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 39.8 KSI
 ULT. STRENGTH: 77.1 KSI
 SPECIMEN THK: 0.493- 0.498"
 SPECIMEN WIDTH: 4.910- 4.915"
 REFERENCES: HD007

STAIN. STEEL
304

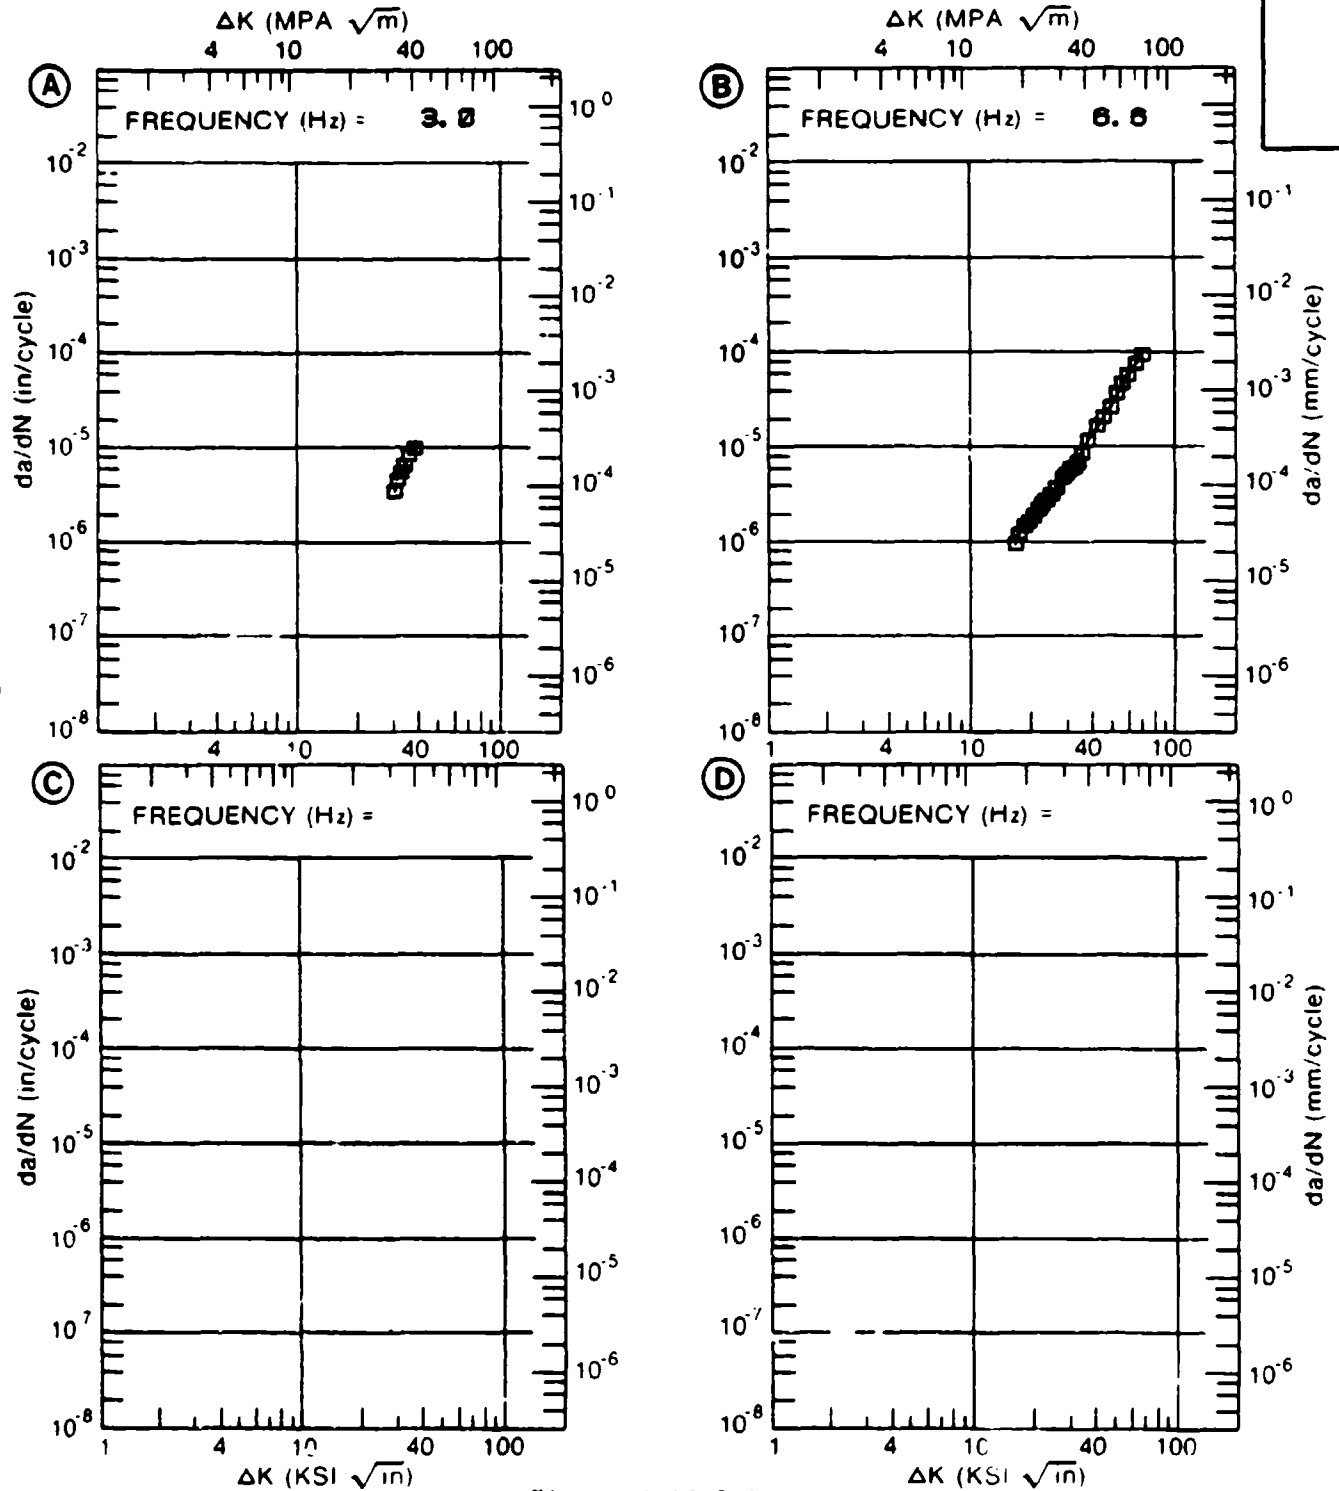


Figure 3.16.3.5

TABLE 3.16.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.16.3.6 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL 304
CONDITION: ANNEALED

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E=+ 800 F			
		AIR			
DELTA K MIN	A:	12.99	1.46		
	B:				
	C:				
	D:				
		13.00	1.46		
		16.00	2.90		
	20.00	5.70			
	25.00	10.3			
	30.00	21.0			
DELTA K MAX	A:	34.83	47.9		
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 15.35
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 4
SUMMARY 1.25-2.0 1
(NP/NA) >2.0

CONDITION/HT: ANNEALED
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION:
 STRESS RATIO: +0.05
 FREQUENCY: 0.6 HZ

YIELD STRENGTH: 39.6 KSI
 ULT. STRENGTH: 77.5 KSI
 SPECIMEN THK: 0.300- 0.500"
 SPECIMEN WIDTH: 1.157- 2.998"
 REFERENCES: HD011, HD012

STAIN.
STEEL

304

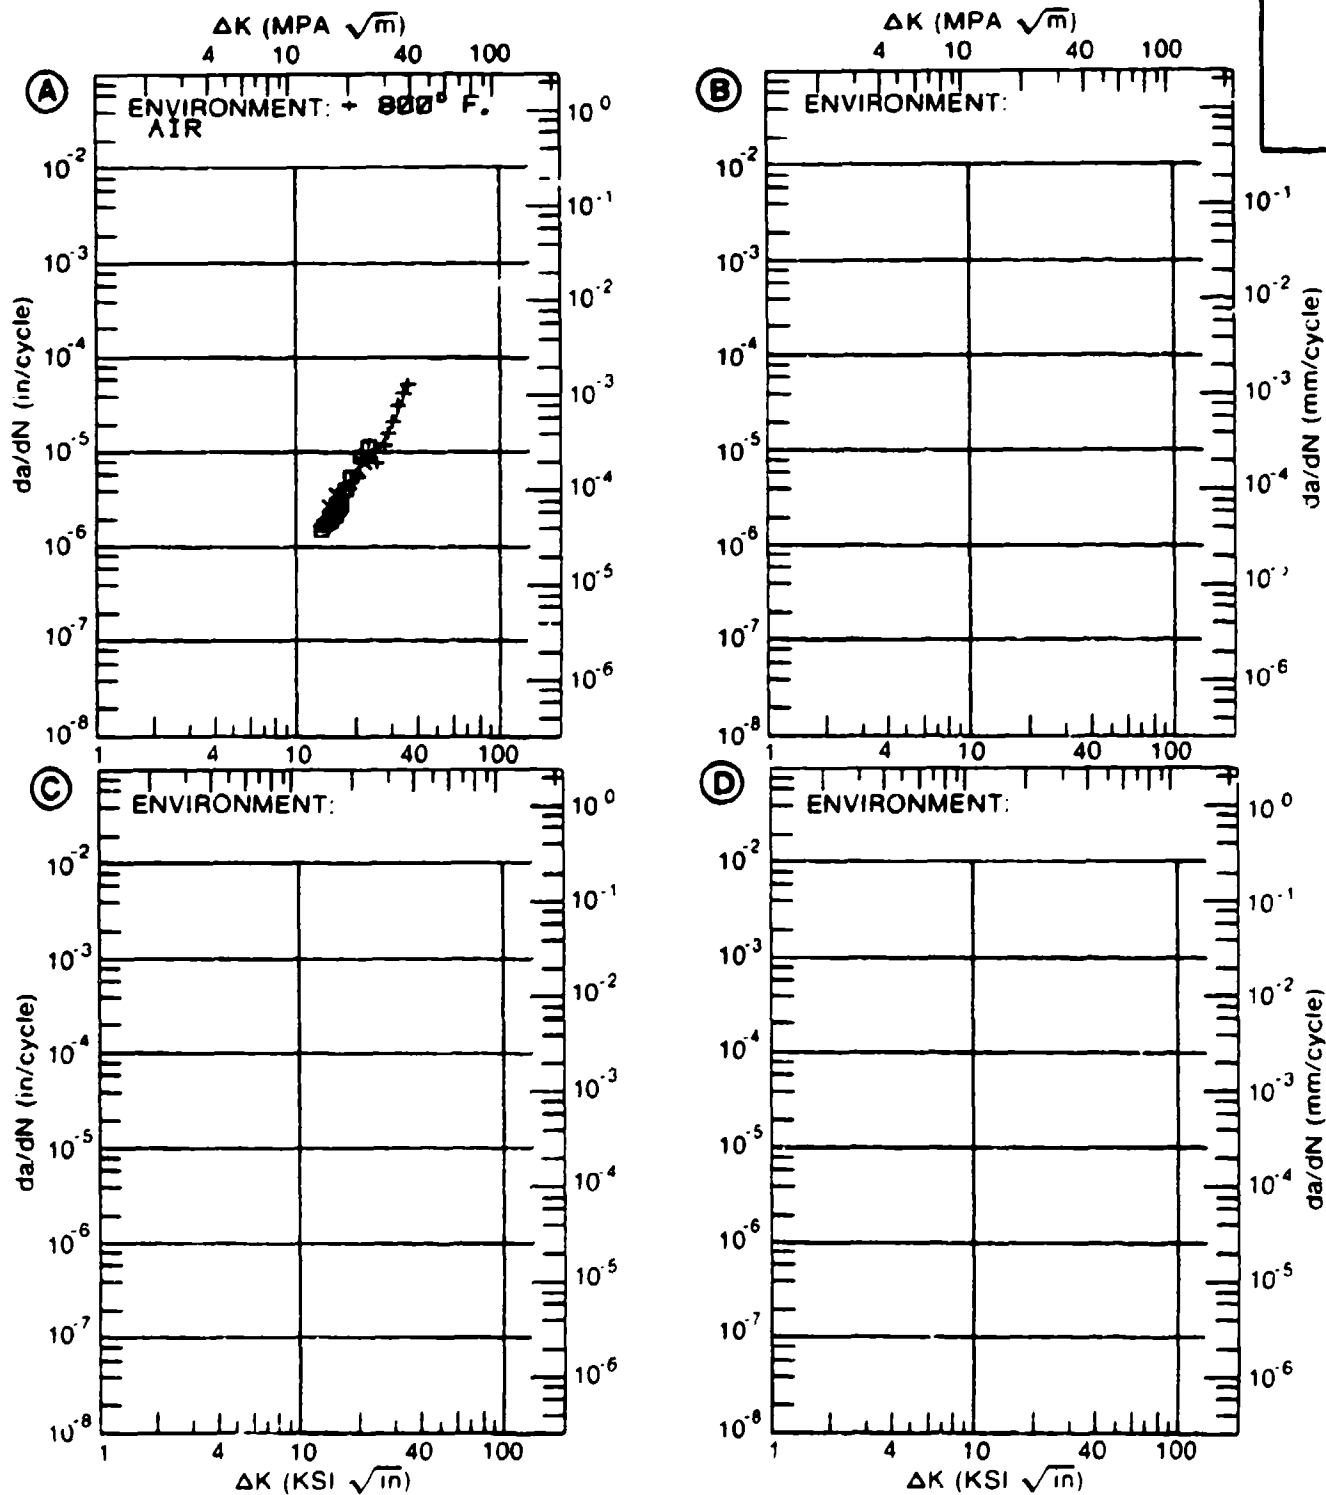


Figure 3.16.3.6

TABLE 3.16.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.16.3.7 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL 304
CONDITION: ANNEALED

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E=+ 550 F			
		: AIR			
DELTA K	A: 17.34	1.23			
MIN	B:				
	C:				
	D:				
	20.00	1.65			
	25.00	4.94			
	30.00	12.0			
	35.00	19.4			
	40.00	36.7			
	50.00	94.3			
DELTA K	A: 51.20	86.4			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 15.97
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: ANNEALED
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.05
 FREQUENCY: 2.5 HZ

YIELD STRENGTH: 39.0 KSI
 ULT. STRENGTH: 84.0 KSI
 SPECIMEN THK: 0.252- 0.999"
 SPECIMEN WIDTH 1.899- 8.001"
 REFERENCES: HD010

STAIN.
 STEEL

304

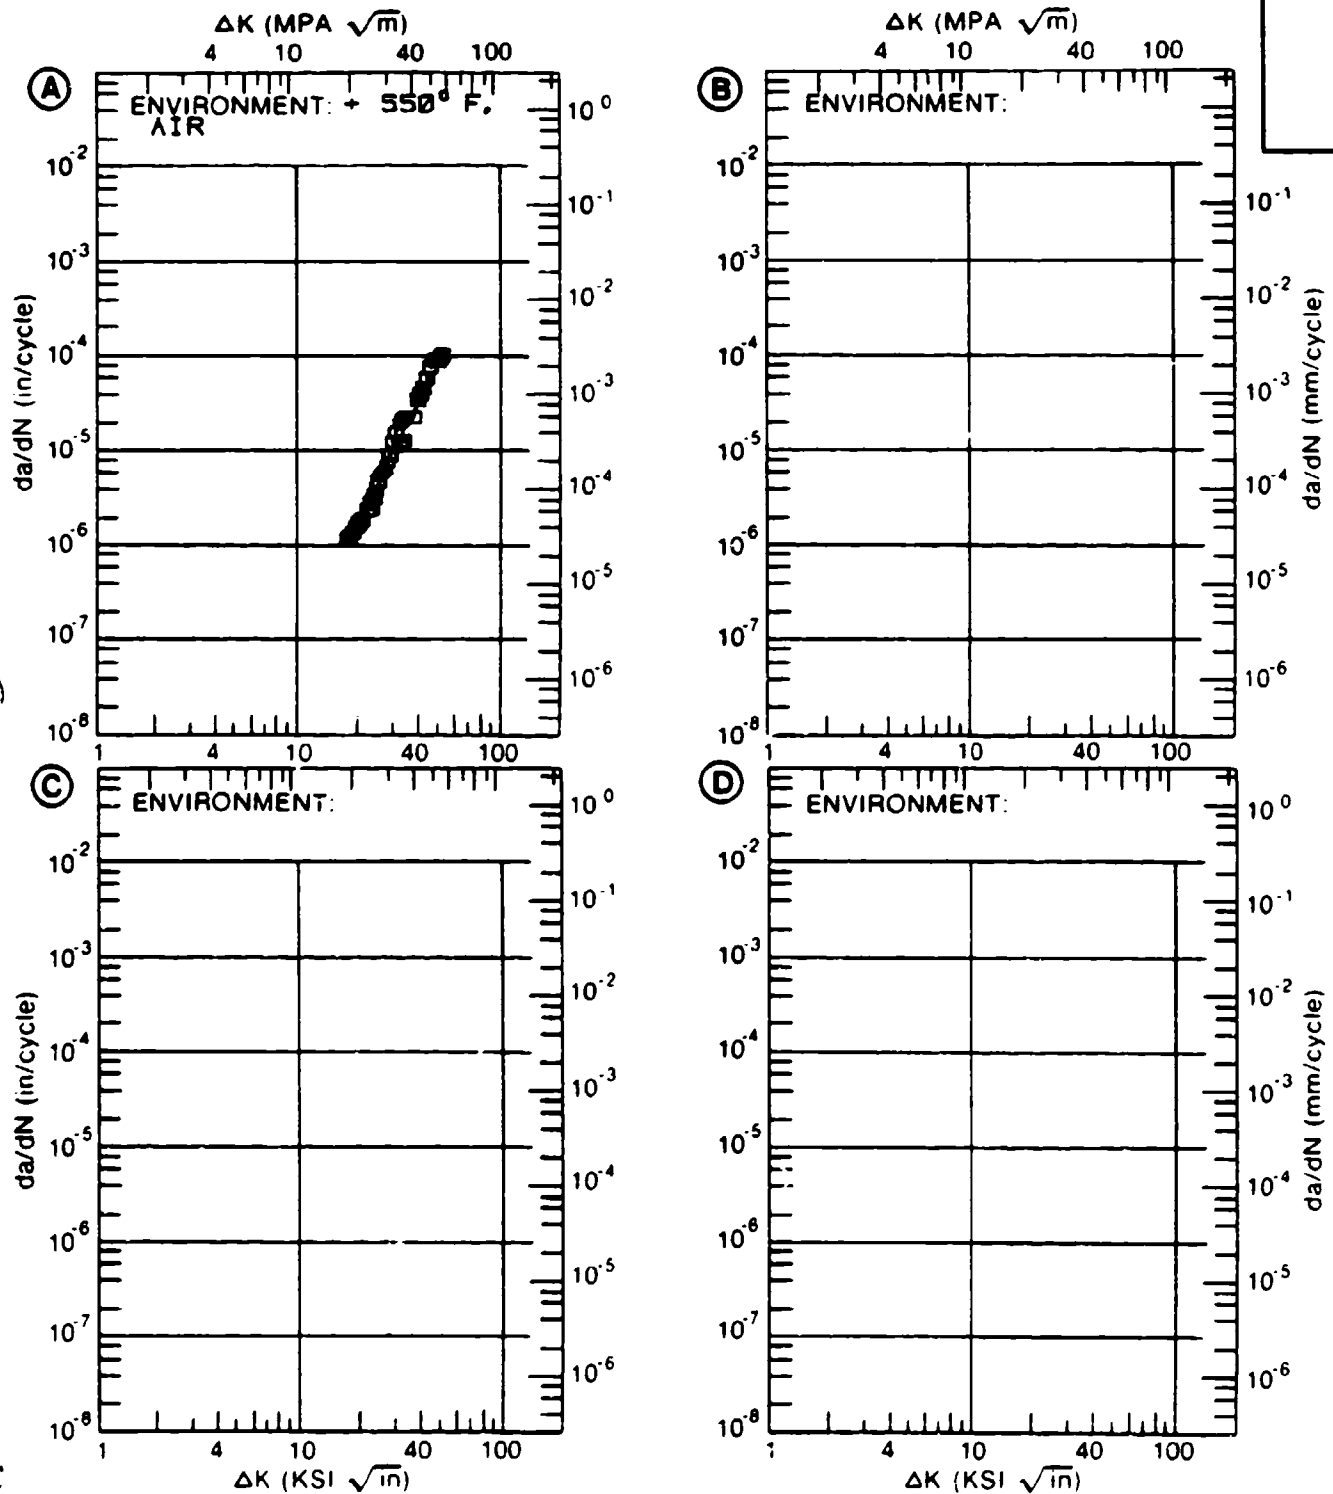


Figure 3.16.3.7

TABLE 3.16.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 3.16.3.8 INDICATING EFFECT
OF ENVIRONMENT-----
MATERIAL: STAINLESS STEEL 304
CONDITION: ANNEALED & AGED

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E = R. T. LAB AIR			
DELTA K	A: 19.08	1.17			
MIN	B:				
	C:				
	D:				
	20.00	1.38			
	25.00	3.99			
	30.00	11.4			
	35.00	27.8			
DELTA K	A: 35.83	31.6			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 8.08
PERCENT ERROR

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	
RATIO	0.8-1.25	1
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: ANNEALED & AGE
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION:
 STRESS RATIO: +0.05
 FREQUENCY: 3.0 HZ

YIELD STRENGTH: 39.6 KSI
 ULT. STRENGTH: 77.1 KSI
 SPECIMEN THK: 0.468"
 SPECIMEN WIDTH: 2.001"
 REFERENCES: H0008

STAIN.
STEEL

304

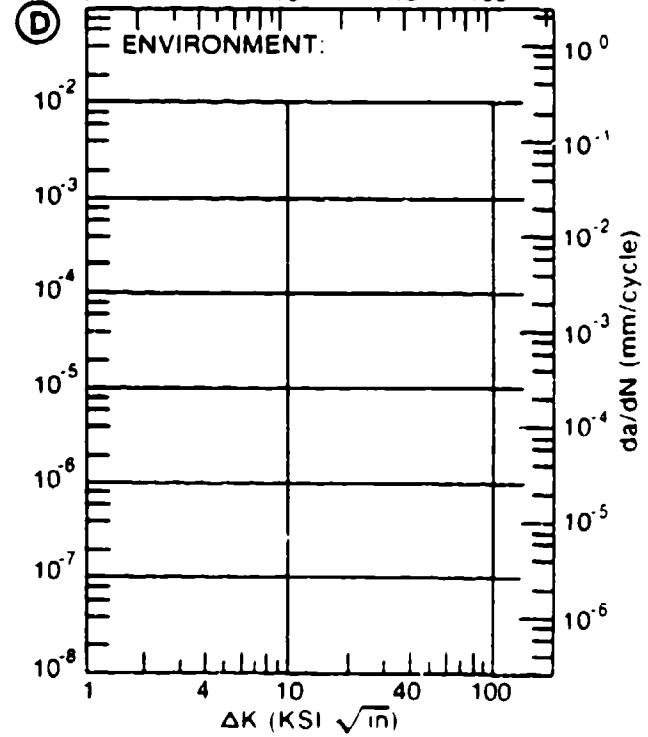
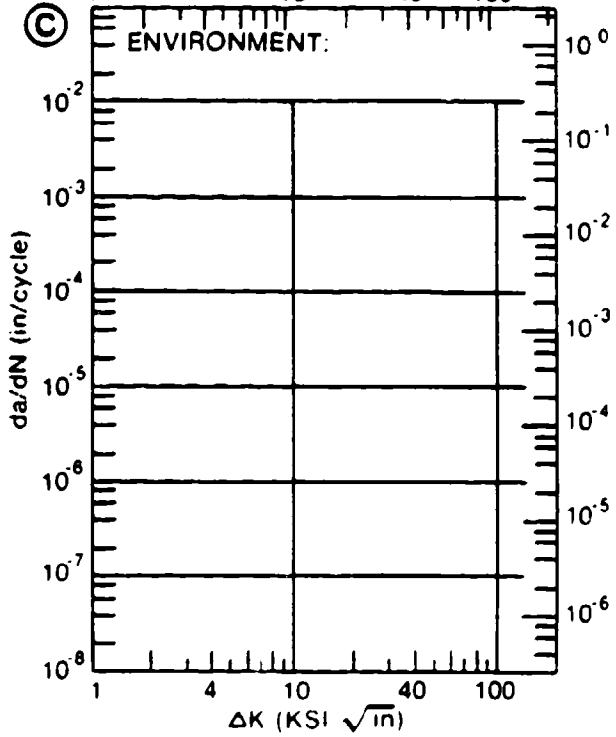
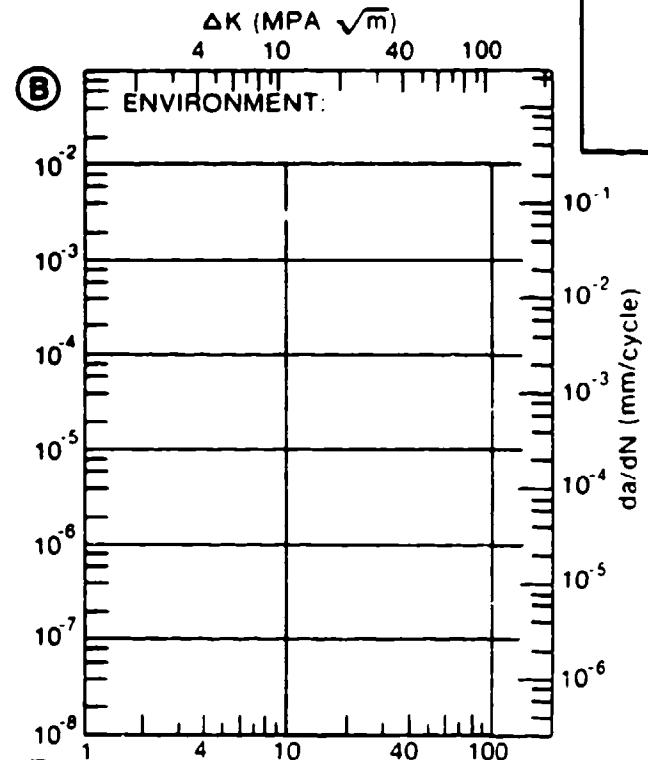
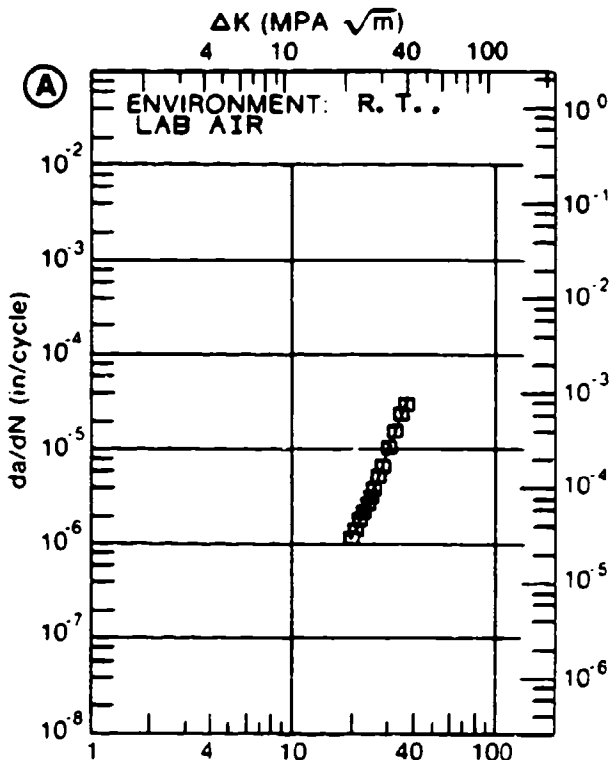


Figure 3.16.3.8

TABLE 3.17.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.17.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL 316
CONDITION: ANNEALED

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E=+ 98 F			
	AIR			
A: 17.85	.435			
DELTA K B:				
MIN C:				
D:				
20.00	.868			
25.00	2.81			
30.00	6.38			
35.00	12.0			
40.00	20.1			
50.00	47.3			
60.00	98.5			
A: 60.48	102.			
DELTA K B:				
MAX C:				
D:				
ROOT MEAN SQUARE	6.93			
PERCENT ERROR				

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	
RATIO	0.8-1.25	1
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: ANNEALED
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: SENT
 ORIENTATION:
 STRESS RATIO: +0.04
 FREQUENCY: 0.8 HZ

YIELD STRENGTH: 44.1 KSI
 ULT. STRENGTH: 82.1 KSI
 SPECIMEN THK: 0.504"
 SPECIMEN WIDTH: 4.501"
 REFERENCES: HD013

STAIN.
 STEEL

318

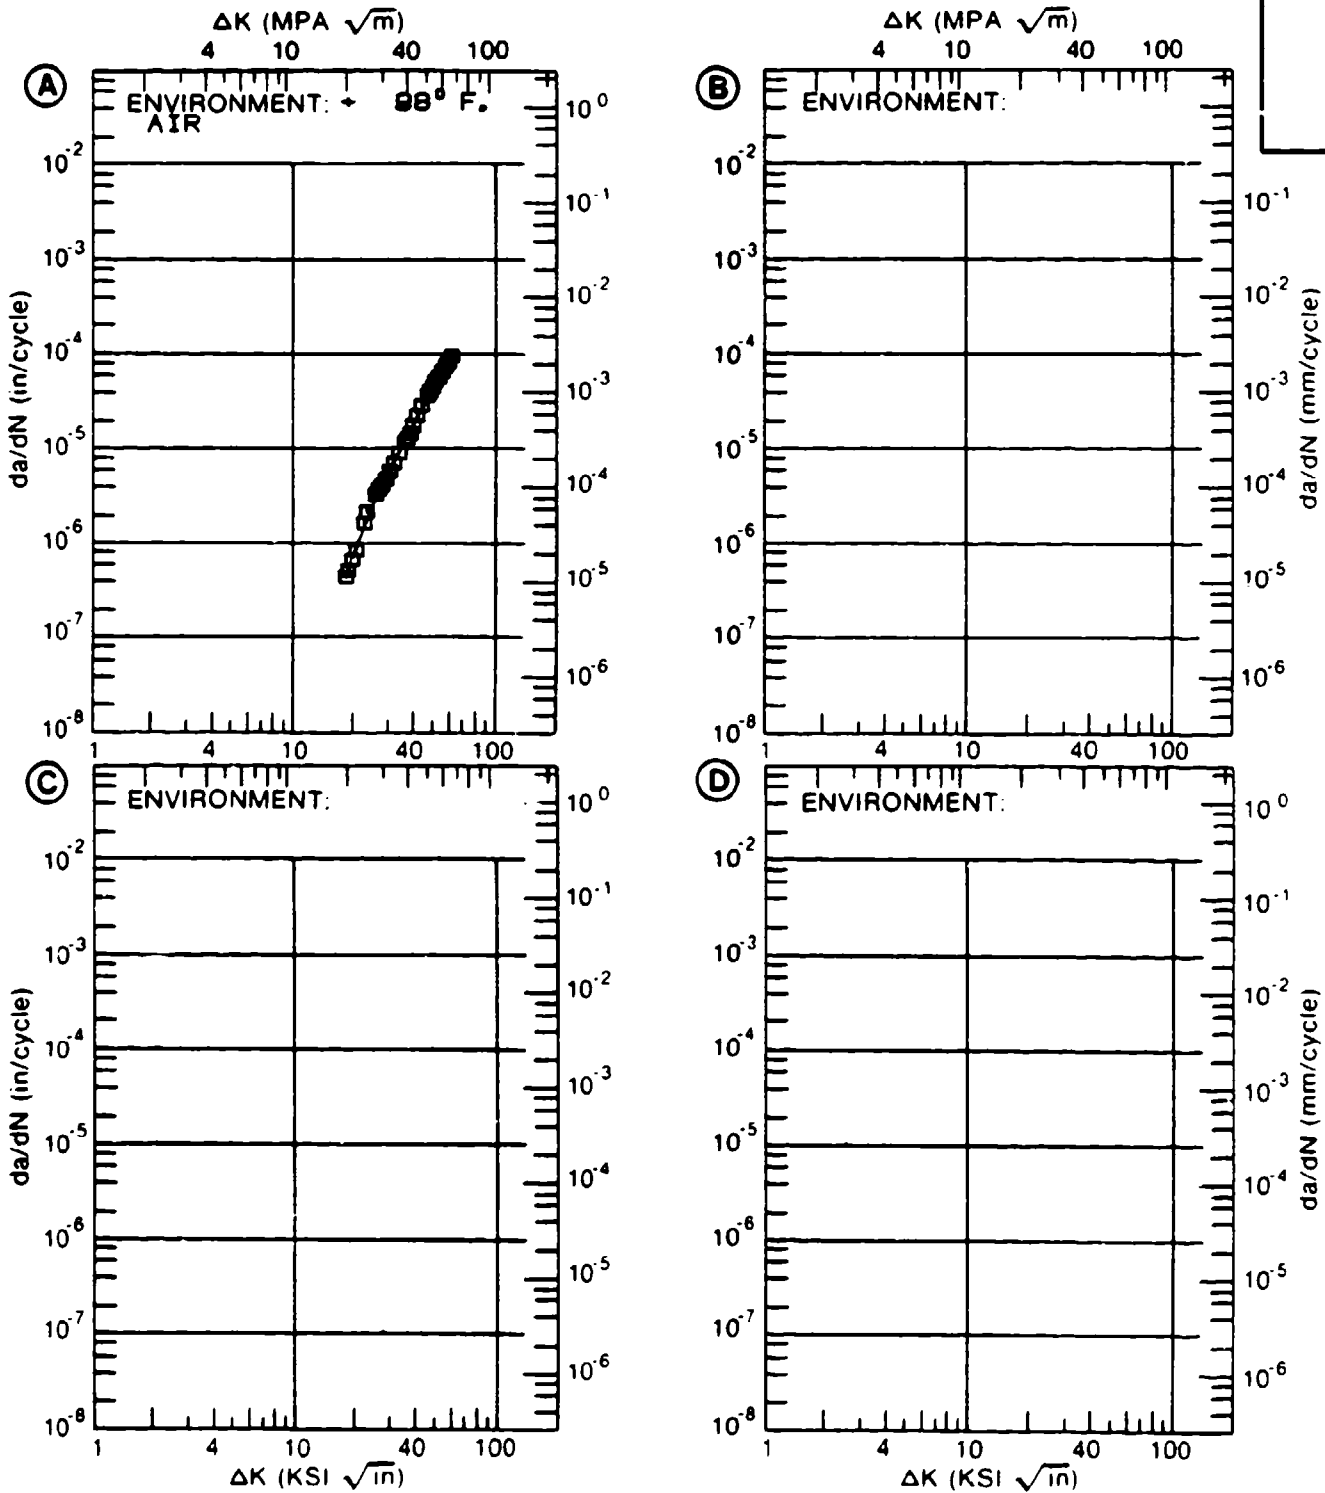


Figure 3.17.3.1

TABLE 3.17.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.17.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: STAINLESS STEEL 316
CONDITION: ANNEALED

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E=+ 600 F	E=+ 800 F		
		AIR	AIR		
DELTA K MIN	A: 13.24	1.10			
	B: 16.21		2.43		
	C:				
	D:				
	16.00	2.02			
	20.00	4.63	5.14		
	25.00	12.5	15.7		
	30.00		35.2		
DELTA K MAX	A: 28.41	18.5			
	B: 30.70		38.1		
	C:				
	D:				
ROOT MEAN SQUARE		14.78	7.64		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	2	1		

CONDITION/HT: ANNEALED
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION:
 STRESS RATIO: +0.05
 FREQUENCY: 0.6 HZ

YIELD STRENGTH: 44.1 KSI
 ULT. STRENGTH: 82.1 KSI
 SPECIMEN THK: 0.486- 0.504"
 SPECIMEN WIDTH: 1.998- 2.047"
 REFERENCES: HD013, HD012

STAIN. STEEL
316

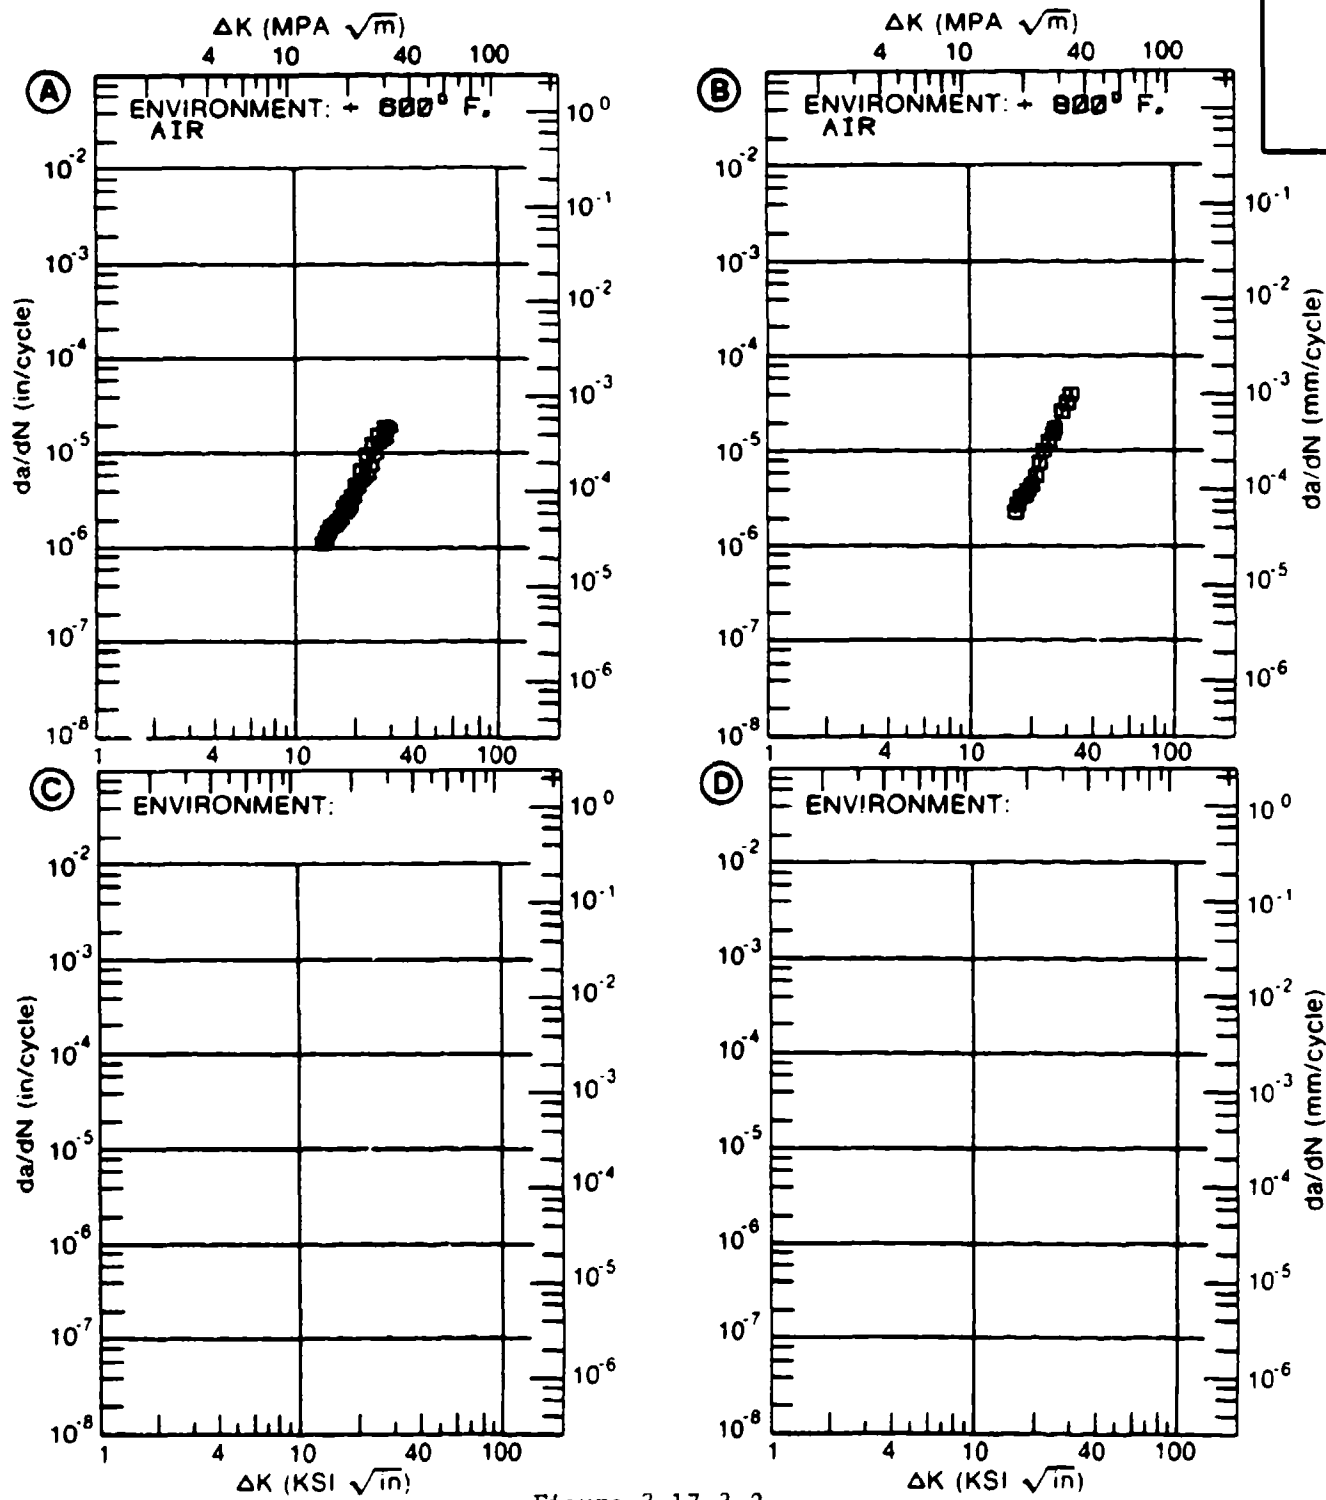


Figure 3.17.3.2

TABLE 3.17.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.17.3.3 INDICATING EFFECT
OF FREQUENCY

MATERIAL: STAINLESS STEEL 316
CONDITION: ANNEALED AT 1950F, 1HR, WG
ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		F(HZ)= 5.00		F(HZ)= 10.00	
DELTA K MIN	A: 21.20	2.84			
	B: 19.09		2.51		
	C:				
	D:				
	20.00		2.39		
	25.00	5.45	6.24		
	30.00	11.6	13.1		
	35.00	22.8	30.9		
	40.00	42.4	53.1		
DELTA K MAX	A: 40.78	46.5			
	B: 40.55		53.6		
	C:				
	D:				
ROOT MEAN SQUARE		4.22	20.54		
PERCENT ERROR					
LIFE PREDICTION	0.0-0.5				
RATIO	0.5-0.8				
SUMMARY (NP/NA)	0.8-1.25	1	1		
	1.25-2.0		1		
	>2.0				

CONDITION/HT: ANNEALED AT 1950F, 1HR, WQ
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION:
 STRESS RATIO: +0.05
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 43.0- 44.1 KSI
 ULT. STRENGTH: 81.5- 82.1 KSI
 SPECIMEN THK: 0.495- 0.525"
 SPECIMEN WIDTH: 2.000- 2.001"
 REFERENCES: HD014, HD013

STAIN. STEEL
316

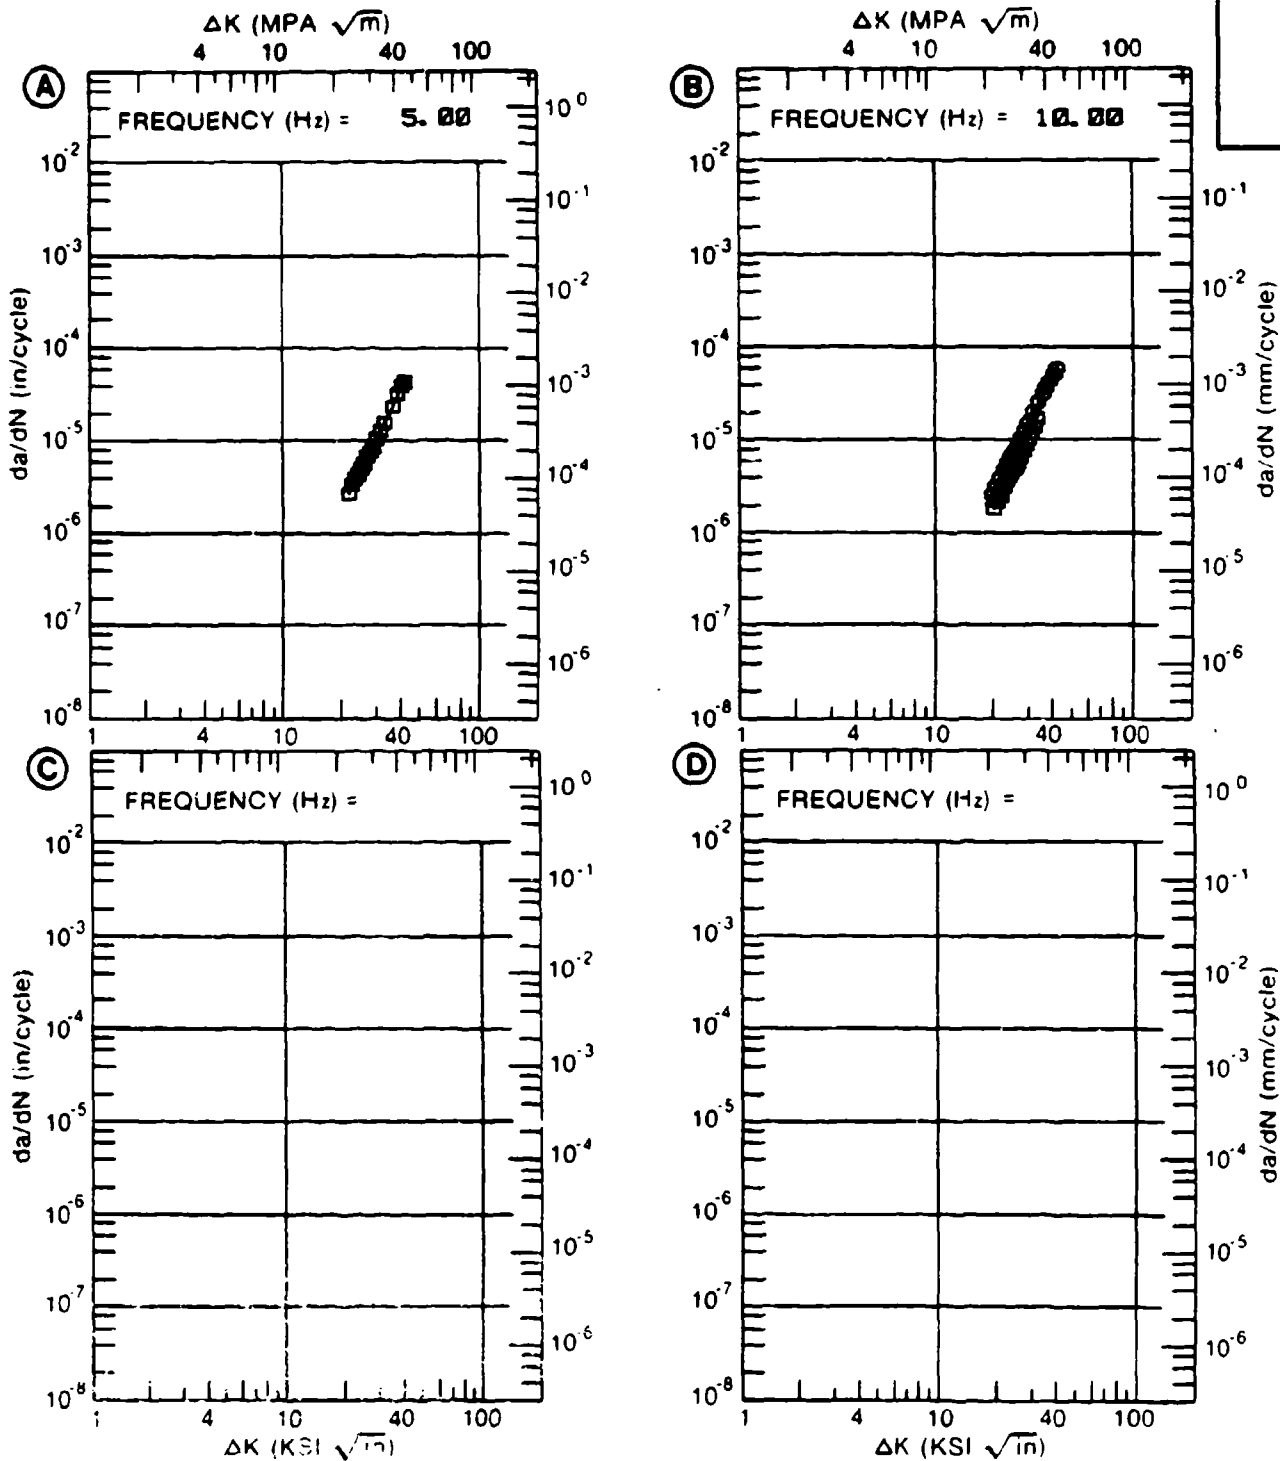


Figure 3.17.3.3

Figure 3.18.1.1

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
STAINLESS STEEL 304

INSPECTION

ENVIRONMENT

LAB AIR
AT R.T.

CRACK LOCATION	WELDMENT	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	30	50	100
FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)											
0.50 IN FROM CENTERLINE	WELDMENT	0.10	30.00								9.83
AT CENTERLINE	WELDMENT	0.10	30.00								12.1
AT HEAT AFFECTED ZONE	WELDMENT	0.10	30.00								17.9

TABLE 3.18.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.18.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 347
CONDITION: AT CENTERLINE
ENVIRONMENT: R.T. LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K	A: 36.67	1.71			
MIN	B:				
	C:				
	D:				
	40.00	3.05			
	50.00	13.1			
	60.00	44.1			
DELTA K	A: 69.67	92.0			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 12.11
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: AT CENTERLINE
 FORM: WELDMENT
 SPECIMEN TYPE: CT
 ORIENTATION:
 FREQUENCY: 30.0 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: AM001

STAIN.
 STEEL

347

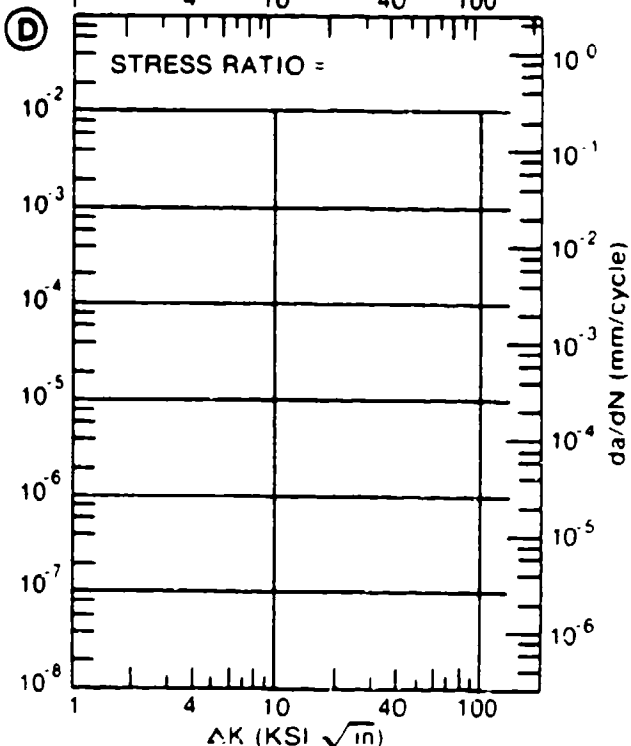
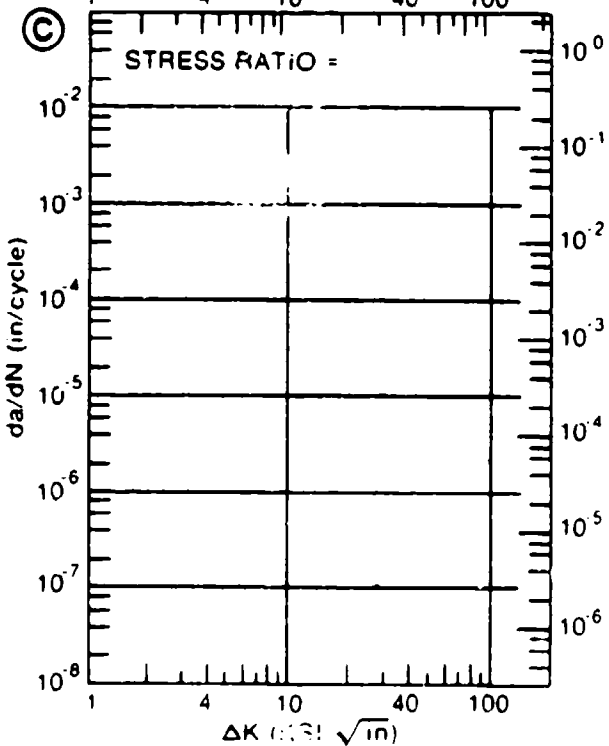
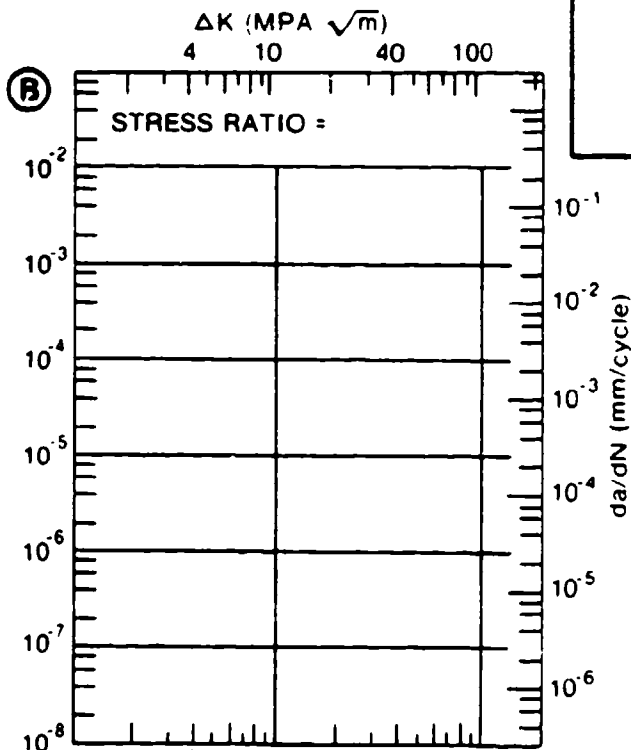
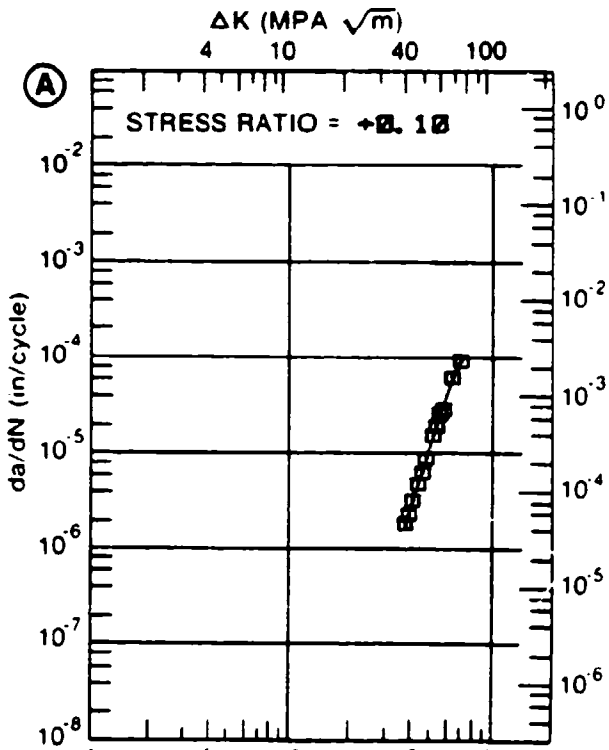


Figure 3.18.3.1

TABLE 3.18.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.18.3.2 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 347
CONDITION: AT HEAT AFFECTED ZONE
ENVIRONMENT: R.T. LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A: 30.61	2.27			
	B:				
	C:				
	D:				
	35.00	4.06			
	40.00	6.87			
	50.00	17.5			
	60.00	46.5			
DELTA K MAX	A: 68.77	121.			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 9.70
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: AT HEAT AFFECTED ZONE
 FORM: WELDMENT
 SPECIMEN TYPE: CT
 ORIENTATION:
 FREQUENCY: 30.0 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: AM001

STAIN.
 STEEL
 347

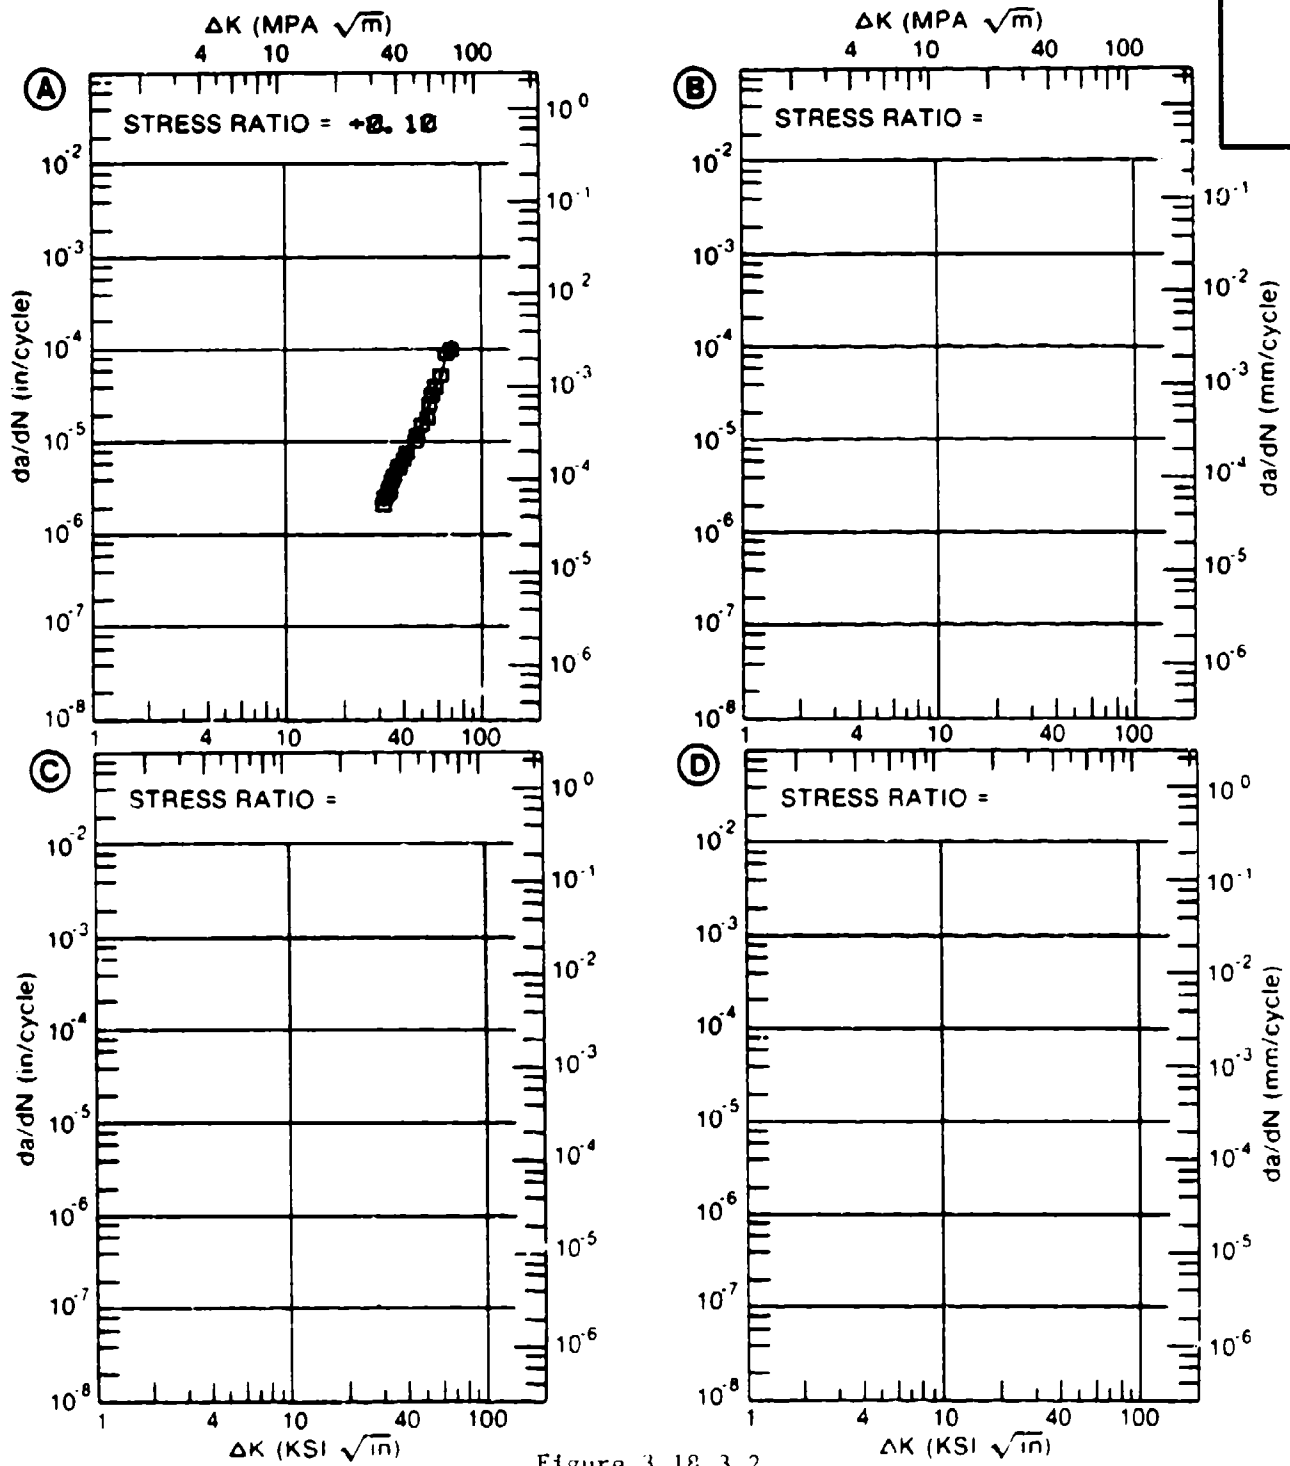


Figure 3.18.3.2

TABLE 3.18.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 3.18.3.3 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: STAINLESS STEEL 347
CONDITION: .050 IN. FROM CENTERLINE
ENVIRONMENT: R. T. LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A: 36.21	2.53			
	B:				
	C:				
	D:				
	40.00	4.98			
	50.00	9.83			
	60.00	18.0			
	70.00	47.3			
	80.00	89.2			
DELTA K MAX	A: 81.77	93.9			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		10.14			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: .050 IN. FROM CENTERLINE
 FORM: WELDMENT
 SPECIMEN TYPE: CT
 ORIENTATION:
 FREQUENCY: 30.0 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: AM001

STAIN.
 STEEL

347

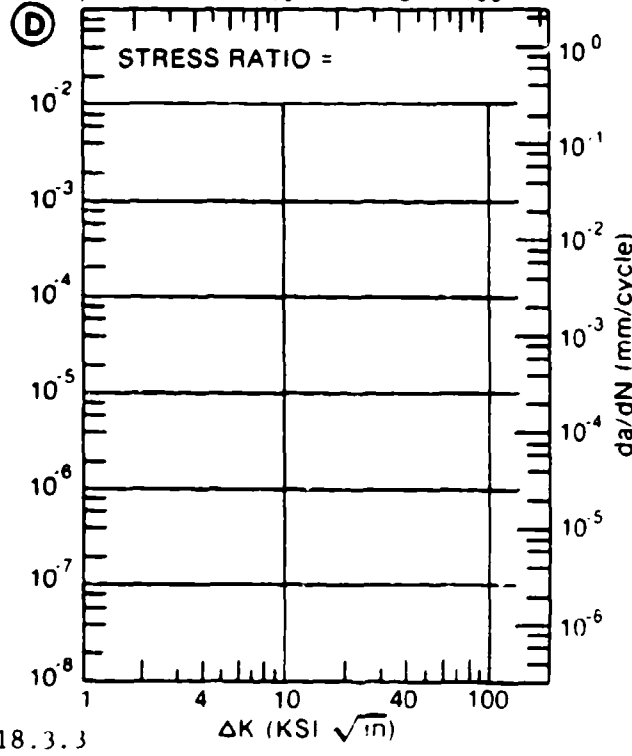
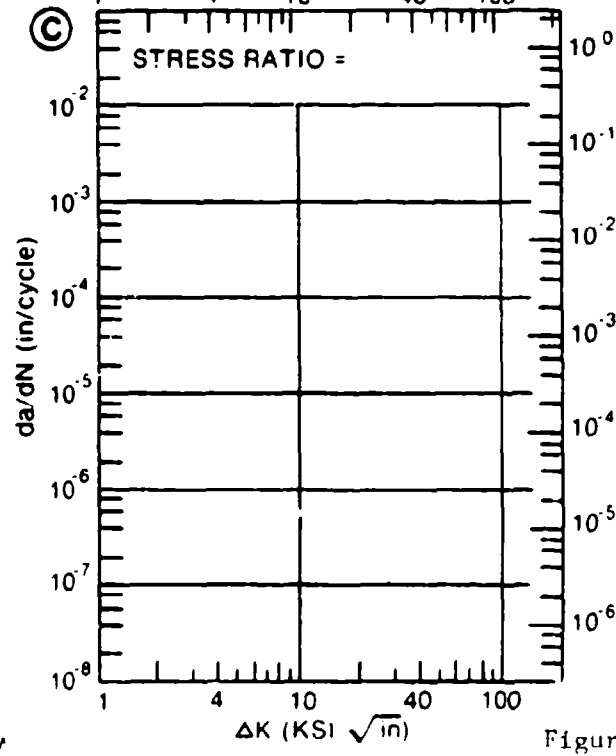
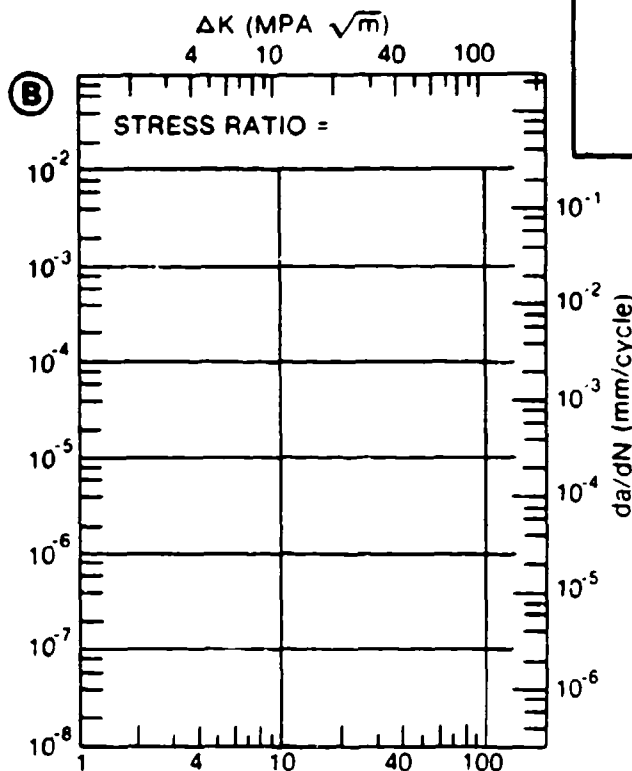
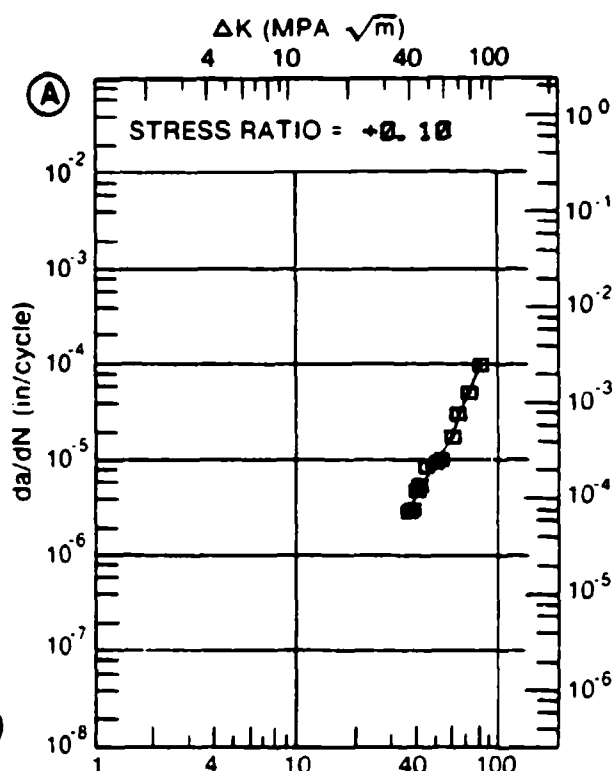


Figure 3.18.3.3

TABLE 3.19
REFERENCES FOR STAINLESS STEEL DATA

57573	PH14-8Mo K _{IC} Anon., "Fracture Toughness and Tear Tests," Air Force Materials Laboratory, Research and Technology Division, Report No. ML-TDR-64-238, October 1964.
70887	PH 13-8Mo K _{ISCC} Peterson, M.H., Brown, B. F., Newbegin, R. L., and Groover, R. E., Stress Corrosion Cracking of High Strength Steels and Titanium Alloys in Chloride Solutions at Ambient Temperature," Corrosion, 23, (5), pp. 142-148, May 1967.
74720	AFC 77 K _{IC} K _{ISCC} Webster, D., "The Use of Deformation Voids to Refine the Austenitic Grain Size and Improve the Mechanical Properties of AFC 77," Research Report D6-23870, The Boeing Co., Renton, WA., ARPA Contract N00014-66-C-0365, February 1969.
76136	AFC 77 K _{IC} K _{ISCC} da/dt Webster, D., "The Stress Corrosion Resistance and Fatigue Crack Growth Rate of a High Strength Martensitic Stainless Steel, AFC 77," Research Report D6-23973, The Boeing Co., Renton, WA., ARPA Contract N00014-66-C-0365, June 1969.
77934	Custom 455 K _{IC} K _{ISCC} Uchida, J. M., "Evaluation of Carpenter Custom 455," Research Report D6-23928, The Boeing Co., Renton, WA., November 18, 1969.
80685	AFC 260 K _{IC} K _{ISCC} Webster, D., "Optimization of Strength and Toughness in Two High Strength Stainless Steels," Metallurgical Transactions, 2, (7), pp. 1857-1862, July 1971.
83613	PH 13-8M K _{ISCC} Sandoz, G., "The Resistance of Some High Strength Steels to Slow Crack Growth in Salt Water," NRL Memorandum Report 2454, Naval Research Laboratory, Washington, D.C., February 1972.
84212	15-5 PH K _{IC} 17-4 PH K _{IC} Takas, E. G., "Fracture Toughness Tests, Data on Armco 17-4PH and 15-5 PH Alloys," letter to J.E. Campbell, Battelle Columbus, October 18, 1972.
84302	AFC 77 K _{IC} Webster, D., "Increasing the Toughness of Martensitic Stainless Steel AFC 77 By Control of Retained Austenite Content, Ausforming and Strain Aging," Transactions of the ASM, 61, (4) pp. 816-838, December 1968.
84306	PH 13-8 Mo K _{IC} Harrigan, M. J., "B-1 Fracture Mechanics Data for Air Force Handbook Usage," Report TFD-72-501, North American Rockwell, Los Angeles Division, Los Angeles, CA., April 21, 1972.
84333	AM 355 K _{ISCC} AM 362 K _{ISCC} AM 364 K _{ISCC} CUSTOM 455 K _{ISCC} PH 13-8 Mo K _{ISCC} PH 15-7 Mo K _{ISCC} 15-5 PH K _{ISCC} 17-4 PH K _{ISCC} 17-7 PH K _{ISCC} Carter, C. S., Farwick, D. G., Ross, A. M., Uchida, J. M., "Stress Corrosion Properties of High Strength Precipitation Hardening Stainless Steels," Corrosion 27, (5), pp. 190-197, May 1971.

TABLE 3.19 (Continued)

84365	PH 13-8Mo K_{Ic} Takacs, E. G., "Plane Strain Fracture Toughness - PH 13-8 Mo," Tabulated Data from Armco Steel Corporation, Advanced Materials Division, Baltimore, Md., July 11, 1972.
85034	PH 13-8 Mo K_{Ic} Mitchell, John, "Laboratory Reports on Fracture Toughness Tests," per memo from Ed Cawthorne of February 5, 1973; data sheets from Shultz Steel Co., South Gate, CA.
85544	AFC 77 da/dN Speidel, M.O., "Dynamic and Static Embrittlement of a High Strength Steel in Water," preprint from L' Hydrogen Dans Les Metaux, 1, Editions Science et Industries, Paris, France (no date).
85836	PH 13-8Mo K_{Ic} "B-1 Fracture Toughness Data (K_{Ic}) - Rockwell International," Rockwell International Corp., Los Angeles, CA., April 24, 1973.
85837	PH 13-8 Mo da/dN "Fracture Toughness Data Collection, Rockwell International Corporation, from B-1 Program," Rockwell International Corporation, Los Angeles, CA., April 1973.
85857	PH 13-8 Mo K_{Ic} Shultz Steel Company - Fracture Toughness Data - May 10, 1973, per memo from Ed. Cawthorne of May 10, 1973.
86688	AM 355 K_{Isc} PH 13-8Mo K_{Isc} PH 15-7 Mo K_{Ic} 15-5 PH K_{Ic} 17-7 PH K_{Ic} K_{Isc} Sprawls, D. O., et al., "Evaluation of Stress Corrosion Cracking Susceptibility Using Fracture Mechanics Techniques," Final Report Part I, Aluminum Co. of America, Alcoa Technical Center, Alcoa, Pa., Contract NASA-21487, May 31, 1973.
87360	AFC 77 K_{Ic} K_{Isc} Caton, R. G., and Carter, C. S., "Evaluation of AFC 77 Martensitic Stainless Steel for Airframe Structural Applications," Report AFML- TR-73-182, Boeing Commercial Airplane Co., Seattle, WA., Contract F33615-71-C-1550, September 1973.
88136	PH 13-8 Mo K_{Ic} Dill, H. D., "Evaluation of Steel Alloys 300M, HP-9Ni-4Co-20, HP-9Ni-4Co - 30, and PH 13-8Mo," Report MDC-A2639, McDonnell Aircraft Co., McDonnell Douglas Corp., St. Louis, Mo., December 21, 1973, with data supplements received May 2, 1974.
88579	PH 13-8Mo da/dN "B-1 Program da/dN Data for Aluminum Alloys," Rockwell International Corporation, Memorandum to H.D. Moran from E.W. Cawthorne Battelle's Columbus Laboratories, April 3, 1974.

TABLE 3.19 (Continued)

90011	PH 13-8Mo K_{Ic} "Rockwell International, B-1 Program Fracture Toughness Data of August 5, 1974," with memorandum from E.W. Cawthorne to H.D. Moran of Battelle's Columbus Laboratories, August 5, 1974.
92270	15-5 PH da/dN Rice, R. L., "Fracture Toughness and Fatigue Crack Propagation in 15-5 PH Stainless Steel Bar," memorandum to J. E. Campbell, Battelle Columbus Laboratories, Columbus, Ohio, January 31, 1975.
AM001	347 da/dN "Fatigue Crack Propagation in a 347 Stainless Steel Weld," Prepared for Airesearch Manufacturing Co., by Del West Associates, Inc., July 29, 1975.
BW004	15-5 PH da/dN Watson, K. R., "Pylon Durability and Damage Tolerance Analysis," The Boeing Co., Wichita, KA., Contract No. F33657-78-C-0108-PZ0036, Document No. D361-400 41-2, September 1980.
BW005	15-5 PH da/dN Watson, K. R., "Weapons Bay Durability and Damage Tolerance Analysis," The Boeing Co., Wichita, KA., Contract No. F33657-78-C-0108-PZ0036, Document No. D361-40041-1, September 1980.
BW007	15-5 PH K_{Ic} Hananel A., Watson, K., Knoff, K., and Sherrich, G., "Fracture Mechanics Testing of B-52/CMI Materials," Final Test Report, The Boeing Co., Wichita, KA., Contract No. F33657-78-C00108-PZ0036, Document No. D361-11197-1, December 1978.
DA001	17-4 PH K_{Ic} da/dN 17-7 PH da/dN Fatigue Crack Growth Rate Data Sheets on Aluminum Alloys 2024, 7010, 7050, 7075, and 7475; Stainless Steel Alloys 17-4 PH and 17-7 PH, and Alloy Steels 4340, A286, H-11, HY-180 and 12-9-2, Sent from Mr. Paul Abelkis, Douglas Aircraft Co., McDonnell Douglas Corp., Long Beach, CA., March 1982.
GD009	PH 13-8 Mo K_{Ic} K_{Isc} da/dN Margolis, W. S., "F-16 Material Allowables Evaluation of PH 13-8Mo Steel Alloy, H1000 Temper," General Dynamics, Fort Worth Division, Report No. 16PR1084, October 1978.
GD010	17-4PH da/dN Margolis, W. S., "Constant Amplitude Fatigue Crack Growth Rate of 17-4 PH Steel Alloy Casting, H1025, Repair Welded and Stress Relieved at 90F," General Dynamics, Fort Worth Division, Report No. 16PR1195, May 1979.
HD007	304 da/dN James, L. A., Schwenk, E. B., "Fatigue-Crack Propagation Behavior of Type 304 Stainless Steel at Elevated Temperatures," Metallurgical Transactions, Vol. 2, pp. 491-496, (1971).
HD008	304 da/dN James, L. A., "Effect of Thermal Aging Upon the Fatigue-Crack Propagation of Austenitic Stainless Steels," Metallurgical Transactions, Vol. 5, pp. 831-838, (1974).

TABLE 3.19 Continued)

HD009	304 da/dN	James, L. A., Staalsund, J. L., Bauer, R. E., "Optimization of Fatigue Crack Growth Testing for First Wall Materials Development Evaluations," Journal of Nuclear Materials, Vol. 85-86, Part B, pp. 851-854, (1979).
HD010	304 da/dN	James, L. A., "Specimen Size Considerations in Fatigue-Crack Growth Rate Testing in Fatigue Crack Growth Measurement and Data Analysis, STD-738, pp. 45-47, ASTM, (1981).
HD011	304 da/dN	James, L. A., "Frequency Effects in the Elevated Temperature Crack Behavior of Austenitic Stainless Steels-A Design Approach," Journal of Pressure Vessel Technology, Vol. 101, pp. 171-176, (1979).
HD012	304 da/dN 316 da/dN	James, L. A., "Some Observations Regarding Specimen Size Criteria for Fatigue-Crack Growth Rate Testing," Report HEDL-TME 77-87, Westinghouse Hanford Co., Richland, WA., August 1977.
HD013	316 da/dN	James, L. A., "The Effect of Elevated Temperature Upon the Fatigue-Crack Propagation Behavior of Two Austenitic Stainless Steels," Mechanical Properties of Materials, Vol. III, pp. 341-352, Society of Materials Science, Japan, 1972.
HD014	316 da/dN	James, L. A., "A Survey of the Effect of Heat-to-Heat Variations Upon the Fatigue-Crack Propagation Behavior of Types 304 and 316 Stainless Steels," Report HEDL-TME 75-37, Westinghouse Hanford Co., Richland, WA., May 1975.
MA001	PH 13-8Mo K_{Ic} da/dN	Fracture Toughness and Fatigue Crack Growth Rate Data for Stainless Steel PH 13-8 Mo. Data supplied by D. L. Rich of McDonnell Aircraft Co., St. Louis, Mo.; Attachment No. 1, Received March 12, 1982.
NC001	PH 13-8 Mo K_{Ic}	Plane Strain Fracture Toughness Data Sets on Aluminum, Steel and Titanium Alloys. Data sent from P.G. Porter of Northrop Corporation, March 1, 1982.
NC002	PH 13-8Mo da/dN	Fatigue Crack Growth Rate Data on Aluminum Steel and Titanium Alloys. Data sent from P.G. Porter of Northrop Corp., March 1, 1982.
RI004	CUSTOM 455 da/dN	Mines, R. G., "Fracture Mechanics Evaluation of Custom 455 Stainless Steel," Rockwell International, Shuttle Orbiter Division, Laboratory Test Report No. 2761-41-33, May 1980
RI006	PH 13-8Mo K_{Isc}	Ferguson, R. R., Berryman, R. C., "Fracture Mechanics Evaluation of B-1 Materials," Rockwell International, B-1 Division, Los Angeles, CA., Contract No. F33657-70-C-0800, Report No. AFML-TR-76-137, October 1976.

CHAPTER 4

TITANIUM ALLOY SECTIONS

- 4.0 Titanium Material Summaries
- 4.1 Beta
- 4.2 Beta C
- 4.3 Beta III
- 4.4 Corona 5
- 4.5 Ti-6Al-2Sn-2Zr-2Mo-2Cr-2.5Si
(also see Section 4.8)
- 4.6 Ti-4Al-3Mo-1V
- 4.7 Ti-5Al-2.5Sn
- 4.8 Ti-6-2-2-2-2 (also see Section 4.5)
- 4.9 Ti-6-2-4-2
- 4.10 Ti-6-2-4-6 (also see Section 4.15)
- 4.11 Ti-6Al-4V
- 4.12 Ti-6Al-4V (ELI)
- 4.13 Ti-6Al-6V-2Sn
- 4.14 Ti-6Al-6V-2.5Sn
- 4.15 Ti-6Al-2Sn-4Zr-6Mo (also see
Section 4.10)
- 4.16 Ti-8Al-1Mo-1V
- 4.17 Ti-8Mo-8V-2Fe-3Al
- 4.18 Ti-5Al-2.5Sn (ELI)
- 4.19 Ti-6Al-6V-2Sn (ELI)
- 4.20 Bibliography

TABLE 4.0.1

AVAILABLE DATA FOR ILLINOIS ALIENS

ITEM	COMPLETION/MT	PRODUCT FORM	KIC	KC	R	CURVES	DA/DM	DA/DT	KISCC
BETA	BETA STAB	SHEET							X
	1745F WA	SHEET							X
	1745F W0. +1095F 61HR	SHEET							X
	1745F W0. +1095F 1000HR	SHEET							X
	1745F W0. +1095F 16HR	SHEET							X
	1745F W0. +1095F .50HR	SHEET							X
1745F W0. +1095F 500HR	SHEET							X	
BETA C	STA	PLATE	X						
	AGED 1000F. 100HR							X	
	AGED 1250F. 50HR							X	
	AGED 900F. 100HR							X	
	BETA STAB +AGED 900F 1HR	SHEET							X
	STA	PLATE					X		
	STA 900F 100HR							X	
	STA 900F 40HR							X	
	STA 900F 0HR							X	
	STA-1325F W0. 1045F 8HR (ELECTRON BEAM WELD ZONE)	PLATE		X					
	STA-1325F W0. 1045F 8HR (HEAT AFFECTED ZONE)	PLATE		X					
	STA-1325F W0. 1045F 8 HR	PLATE		X					
STA C. B WELDMENT (WELD ZONE)	WELDMENT						X		
STA. E. B WELDMENT (HEAT AFFECTED ZONE)	WELDMENT						X		

TABLE 4.0.1 (Cont)

AVAILABLE DATA FOR LITHIUM ALLOYS

ALLOY	CONDITION/T	PRODUCT FORM	KTC	KC	R CURVES	DA/EN	DA/DT	KISCC
BETA III	1025F 27HR. NO 925F 8HR	PLATE	X					
	1750F 0.5 HR. NO. 925F 8HR. AC	EXTRUSION	X					
BETA II	BETA STABILIZED	SHEET					X	
BETA C	SIA	SHEET				X		
CONDITION 5	ALPHA BETA FORGED & LOW ANNEAL 8 HR.	FORGING	X					
TI 5A1 2 55N(F11)	ANNEALED	FORGING	X					
	ANNEALED (ES)	FORGING	X					
	ANNEALED (IS)	FORGING	X					
TI 6A1 605N(F11)	1605F 1 HR. NO. 1070F 4 HR. AC	PLATE	X					
	1650F 1 HR. NO. 1125F 4 HR. AC	PLATE	X					
TI 4A1 300F 10	MILL ANNEALED	PLATE						X
TI 5A1 2 55N	--	SHEET				X		
	ANNEALED	SHEET		X				
TI 6A1 605N/HAPO	BETA PROCESSED	FORGING	X					
	RU. B FIN 10MA BETA UPSET.	FORGING	X					
	BETA FINISH D. 10% PRIMARY ALPHA							
	MILL ANNEALED 1500F 1 HR. AC							
	RU. B FIN 105TA BETA UPSET.	FORGING	X					
	BETA FINISHED 10% PRIMARY ALPHA.							
	SOLUTION TREATED & AGED							
	1625F 1 HR. AC 1100F 8 HR. AC							

TABLE 4.0.1 (Cont)

AVAILABLE DATA FOR TITANIUM ALLOYS

ALLOY	CONDITION: HT	PRODUCT FORM	K1C	KIC	R CURVES	DA/DN	DA/DT	KISCC	
Ti-6Al-2Sn-1Zr-0.1Pd	BU, B FIN-10% BETA UPSET BETA FINISHED, 10% PRIMARY ALPHA SOLUTION TREATED/COVERAGED 1625F 1 HR. AC, 1700F 1 HR. AC	FORGING	X						
	BU, B FIN-50% BETA UPSET, BETA FINISHED, 50% PRIMARY ALPHA, MILL ANNEALED 1300F 1 HR. AC	FORGING	X						
	TU, B FIN-50% BETA UPSET, BETA FINISHED, 50% PRIMARY ALPHA, SOLUTION TREATED & AGED, 1625F 1 HR. AC, 1100F 8 HR. AC	FORGING	X						
	BU, HAFIN10% BETA UPSET, HI ALPHA BETA FINISHED, 10% REDUCTION, SOLUTION TREATED & AGED, 1625F 1 HR. AC, 1100F 8 HR. AC	FORGING	X						
	BU, HAFIN20% BETA UPSET, HI ALPHA BETA FINISHED, 30% REDUCTION, SOLUTION TREATED & AGED, 1625F 1 HR. AC, 1100F 8 HR. AC	FORGING	X						
	BU, LABFIN10% BETA UPSET, LO ALPHA BETA FINISHED, 10% REDUCTION, SOLUTION TREATED & AGED, 1650F 1 HR. AC, 1100F 8 HR. AC	FORGING	X						
	STA 1625F 2 HR. AC, 1100F 8 HR. AC	FORGING	X						
	50% PRIMARY ALPHA	FORGING	X				X		X
	AB FORGED-MA ALPHA-BETA FORGED, MILL ANNEALED	FORGING	X						
	AB FORGED-RA ALPHA-BETA FORGED, RECRYSTALLIZED ANNEAL 1700F 4 HR. FC, TO 1000F 1 AC	FORGING	X						

Ti-6Al-4V

TABLE 4.0.1 (Cont)

AVAILABLE DATA FOR TITANIUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	KIC	KC	R	CURVES	DA/DN	DA/DT	MISCC
11-GAL-4V	ALPHA-BETA FORGED	FORGING					X		
	ANNEALED	FORGING	X						
		EXTRUSION	X						
		BILLET	X				X		
		SHEET		X					
	ANNEALED AT 1375F. 3HRS. AC	PLATE					X		
	ANNEALED 1000F 2 HR. AC	BILLET	X						
	ANNEALED 1300F 4 HR. AC	FORGING	X						
	ANNEALED 1375F 3HR. AC	PLATE	X						
	ANNEALED 2700F 2 HR	FORGING	X						
	AS RECEIVED	FORGED BAR	X						
	AS RECEIVED PROBABLY MA	PLATE							X
	AS RECEIVED (ALPHA-BETA FORGED)	FORGED BAR	X						
	AS WELDED (B WELDMENT (WELD ZONE))	WELDMENT					X		
	AS WELDED (B WELDMENT (HEAT AFFECTED ZONE))	WELDMENT					X		
	B FORGED BETA FORGED REHEATED TO 1950F DRAIN TO SIZE. ANNEALED 1300F	FORGED BAR	X						
	B FORGED MA BETA FORGED. MILL ANNEALED. 1300F 2 HR. AC	FORGING	X						
	BA	SHEET					X		
		PLATE					X		
		FORGING					X		

TABLE 4.0.1 (Cont)

AVAILABLE DATA FOR TITANIUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	K1C	KIC	R CURVES	DA/DN	DA/DT	KISCC	
Ti-6Al-4V	RR-AB FINISHED BETA BLOCKED. ALPHA BETA FINISHED. 10% REDUCTION. SOLUTION TREATED & OVERAGED 1750F 1HR. MO. 1500F 2 HR. AC	FORGING		X					
	DR-AB FINISHED BETA-BLOCKED. ALPHA BETA FINISHED. 30% REDUCTION. SOLUTION TREATED & OVERAGED 1750F 3HR. MO. 1500F 2 HR. AC	FORGING		X					
	RR-AB FIN-MA BETA BLOCKED. ALPHA-BETA FINISHED. MILL ANNEALED	FORGING		X					
	DR-AB FIN-RA BETA BLOCKED. ALPHA BETA FINISHED. RECRYSTALLIZED. ANNEAL 1700F 4 HR. FC TO 1000F. AC	FORGING		X					
	RR-AB FIN-30MA BETA BLOCKED. ALPHA BETA FINISHED. 30% REDUCTION. MILL. ANNEALED. 1500F 2 HR. AC	FORGING		X					
	RR-0 FINISHED BETA FINISHED. 10%REDUCTION. SOLUTION TREATED & OVERAGED. 1750F 1 HR. MO. 1500F 2HR. AC	FORGING							
	RR-0 FIN-10MA BETA BLOCKED. BETA FINISHED. 10%REDUCTION. MILL. ANNEALFD. 1500F 2 HR. AC	FORGING		X					
	BETA ANNEALED	PLATE		X					
	BETA FORCED	FORGING						X	
	BETA PROCESSED-MILL ANNEALED	SHEET PLATE		X				X	X

TABLE 4.0.1 (cont)

AVAILABLE DATA FOR TITANIUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	K1C	KIC	R CURVES	DA/DN	DA/DT	MISCC
Ti-6Al-4V	DB	PLATE				X		
	DB + 1H	PLATE				X		
	DR + 2DBTC	PLATE				X		
	DB + 4DBTC	PLATE				X		
	DB1 + PC	PLATE				X		
	DBTC	PLATE				X		
	DDTC (HA)	PLATE				X		
	DIFFUSION BOND	PLATE	X					
	DIFFUSION BOND	BILLET	X					
	DIFFUSION BOND ANNEALED	BILLET	X					
	EB WELD, STRESS RELIEVED (HEAT AFFECTED ZONE)	WELDMENT					X	
	CR WELD, STRESS RELIEVED (WELD ZONE)	WELDMENT					X	
	FINISH ROLLED 1340F	PLATE						X
	GTA WELD POSTWELD 1200F 1HR (HEAT AFFECTED ZONE)	PLATE						X
	GTA WELD POSTWELD 1400F 1HR (HEAT AFFECTED ZONE)	PLATE						X
GTA WELD POSTWELD 1100F 2HR (WELD ZONE)	PLATE						X	
GTA - WELD POSTWELD 1100F 2HR (HEAT AFFECTED ZONE)	PLATE						X	

TABLE 4.0.1 (Cont)

AVAILABLE DATA FOR TITANIUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	K1C	KIC	R	CURVES	DA/DN	DA/DT	KISCC
Ti-6Al-4V	MA	PLATE		X			X		
		SHEET		X			X		
		EXTRUSION FORGING					X		
		MA COARSE GRAIN 1300F 2 HR.AC	FORGING	X					
		MA FINE GRAIN 1300F 2 HR.AC	FORGING	X					
		MA 10-20%ALPHA 10 TO 20% PRIMARY ALPHA MILL ANNEALED 1300F 2 HR.AC	FORGING	X					
		MA 1300F 2HRS AC	DISK				X	X	
		MA 40 50%ALPHA 40 TO 50% PRIMARY ALPHA MILL ANNEALED 1300F 2 HR.AC	FORGING	X					
		MILL ANNEALED	PLATE SHEET	X					X X
		MILL ANNEALED 1300F 2HR.AC	EXTRUSION FORGING BILLET	X X					
	MINUTEMAN CASTING	PLATE						X	
	RA	PLATE FORGING					X X	X X	
	RA(FAST COOLED)	PLATE					X		
	RECRYSTALLIZE ANNEAL	PLATE FORGING	X X						

TABLE 4.0.1 (Cont)

AVAILABLE DATA FOR TITANIUM ALLOYS

ALLOY	CONDITION/TIT	PRODUCT FORM	K1C	KIC	R CURVES	DA/DN	DA/DT	KISCC
T1 6AL-4V	SDR TREATED 1050F 4HR. WELDED 1050F 4HR	FORGING						X
	SOL TREATED 1050F 4+4 HR	FORGING						X
	STA	PLATE FORGING	X					
		PLATE FORGING	X			X		
	STA 1750F 1 HR. AC. 1300F 2 HR. AC	FORGING	X					
	STRESS RELIEVED E B WELDMENT (WELD ZONE)	WELDMENT				X		
	STRESS RELIEVED E B WELDMENT (WAT AFFECTED ZONE)	WELDMENT				X		
	WELDED & STRESS RELIEVED 1100F 2HRS (HAZ)	WELDMENT				X		
	1000F 2HR	FORGING					X	
	1300F 1HR. AC	FORGING		X				
	1300F 2HR AC	EXTRUSION						X
	1450F. 1HR. AC	PLATE	X					
1550F 4HRS T.C. 1700F 4HRS ARGON COOLED	FORGING				X			
1700F 4HR F.C. TO 1400F AC. DIFFUSION BOND THERMAL CYCLE	PLATE						X	
1700F 5 HR. AC. 1400F 6 HR. AC	FORGING		X					

TABLE 4.0.1 (Cont)

AVAILABLE DATA FOR TITANIUM ALLOYS

ALLOY	CONDITION/THT	PRODUCT FORM	KIC	KC	R CURVES	FA/DN	DA/DT	MISCC
Ti-6Al-4V	1725F 1HR WQ 1250F 4HR AC (STDA)	EXTRUSION						X
	1725F 1HR WQ 1000F 1HR AC (STA)	EXTRUSION						X
	1750F WQ 1000F 8HR 1000F (ALPHA+ETA)	FORGING						X
	1750F 1 HR. WQ. 1000F 4 HR	FORGING	X					
	1750F 1HR FC TO 1100F. AC	PLATE	X					
	1750F 1HR. FC TO RT	PLATE	X					
	1750F 1000F 2HR AC	FORGING		X				X
	1750F 2 HR. FC TO 900F AT 100F/HR. AC	FORGING	X					
	1750F 2HR. WQ. 1000F 2HR. AC. 1000F 2HR. AC. STA	PLATE	X					
	1770F 1 2HR WQ 1050F-1100F 8HR. 950F 8HR	FORGING						X
	1750F 3HRS ARGON COOLED. 100 OF 4HRS ARGON COOLED	FORGING			X			
	1775F 1HR WQ. 1675F 1HR WQ. 1000F 4HRS AC. 900F 5HRS AC	DISK			X			
	1775F 1HR WQ. 1575F 1HR WQ. 1000F 1200F 2-8HRS AC	DISK			X			
	1750F 1 5HR WQ 1150F 8HR + 1020F 8HR AC	SHEFT						X
1500F 0 5HR 675F 2HR AC	PLATE							
1950F 4HRS WQ. 1000F 4HRS ARG ON COOLED	FORGING					X		

TABLE 4.0.1 (Cont)

AVAILABLE DATA FOR TITANIUM ALLOYS

ALLOY	CONDITION/T	PRODUCT FORM	K1C	KIC	KC	R CURVES	DA/DN	DA/DT	KISCC
Ti-6Al-4V (ELI)	ANNEALED	SHEET			X				
	BA	PLATE					X		
Ti-6Al-4V (ELI)	ANNEALED	FORGING	X					X	
	BA	PLATE						X	
	RECRYSTALLIZED ANNEAL	PLATE	X						
	1800F 1HR HELIUM COOL	PLATE							X
Ti-6Al-6V-2Zr	ANNEALED 10-20-10-20% PRIMARY ALPHA ANNEALED 1350F 2 HR. AC	FORGING		X					
	ANNEALED 40-50-40-50% PRIMARY ALPHA ANNEALED 1350F 2 HR. AC	FORGING		X					
	ANNEAL-COARSE GRAIN-1350F 2 HR. AC	FORGING							
	ANNEAL-FINE GRAIN 1350F 2 HR. AC	FORGING		X					
	BA	PLATE						X	
	BA 10-10-10% BETA BLOCKED. ALPHA-BETA FINISHED 10% REDUCTION. SOLUTION TREATED & OVERAGED 1650 1 HR. WQ 1300F 2 HR. AC	FORGING		X					
Ti-6Al-6V-2Zr	BA 10-10-10% BETA BLOCKED. ALPHA-BETA FINISHED 10% REDUCTION. MILL ANNEALED 1350F 2 HR. AC	FORGING		X					
	BA 10-10-10% BETA BLOCKED. ALPHA-BETA FINISHED 10% REDUCTION. SOLUTION TREATED & OVERAGED 1650 1 HR. WQ 1300F 2 HR. AC	FORGING		X					

TABLE 4.0.1 (Cont)

AVAILABLE DATA FOR TITANIUM ALLOYS

ALLOY	CONDITION/THT	PRODUCT FORM	MTC	KC	R CURVES	DA/DN	DA/DT	MISCC
Ti-6Al-4V-2Sn	BB, AB FIN-30MA BETA BLOCKED. ALPHA BETA FINISHED. 10% REDUCTION. MILL ANNEALED 1350F 2 HR. AC	FORGING	X					
	BB, B FIN-10 BETA BLOCKED. BETA FINISHED. 10% REDUCTION. SOLUTION TREATED & OVERAGED. 1550F 1 HR. WQ. 1300F 2HR. AC	FORGING	X					
	BB, P FIN-10MA BETA BLOCKED. BETA FINISHED. 10% REDUCTION. MILL ANNEALED 1350F 2 HR. AC	FORGING	X					
	BETA ANNEAL	PLATE	X					
	BETA ANNEAL 1810F 1 HR. ARGON COIL	PLATE	X					
	BETA ANNEAL & STUA-1800F 0.5HR. AC. 1575F 0.5HR. WQ. 1050F 8 HR. AC	PLATE	X					
	BF, AB FOR-ANN BETA FLECTED. ALPHA BETA FORGED. ANNEALED. 1350F 2 HR. AC	FORGING	X					
	BF, B FOR-ANN BETA FLECTED. BETA FORGED. ANNEALED 1350F 2 HR. AC	FORGING	X					
	PF, AB FOR-ANN BETA FLECTED. LOW ALPHA BETA FORGED (1500F) ANNEALED. 1350F 2 HR. AC	FORGING	X					
	DUPLEX ANNEAL	PLATE	X					
	MA	----- EXTRUSION FORGING						X X X
	MILL ANNEALED	PLATE FORGING	X X					

TABLE 4.0.1 (Cont)

AVAILABLE DATA FOR LIQUIDUS ALLOYS

ALLOY	CONDITION/THT	PRODUCT FORM	K1C	KIC	KC	R	DA/DN	DA/DT	K1SCC
71 AAL (V. 25N)	MILL ANNEALED	FORGED BAR	X						
		HILLET	X						
	MILL ANNEALED 1000F 2 HR. AC	PILLET	X						
	PA								X
	RECRYSTALLIZE ANNEAL	PLATE	X						
	STA-1450F 0.5HR. WQ. 1050F 6 HR. AC	FORGING	X						
	STA-1650F 0.5HR. WQ. 1050F 24 HR. AC	FORGING	X						
	STA-1675F 0.25 HR. WQ. 1100F 4 HR	PLATE	X						
	STDA	PLATE							X
	STDA-1500F 1 SHP. WQ. 1250F 6 HR. AC	EXTRUSION	X						
	STDA-1450F 1 HR. WQ. 1300F 2 HR. AC	FORGING	X						
	STDA 1700F 1 HR. WQ. 1400F 1 HR. AC	PLATE	X						
	1700F 2HR	HILLET FORGING	X						X
	1650 1 HR. WQ.	FORGING	X						
	1675F 2 HR. AC 1600F 1 HR. FC	PLATE	X						
	1675F 2 HR. AC 1600F 1 HR. FC	FORGING	X						
	1675F 2 HR. AC 1800F 1 HR. FC	FORGED BAR	X						

TABLE 4.0.1 (Cont)

AVAILABLE DATA FOR TITANIUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	KIC	MC	R	CURVES	DA/DN	DAY/DT	MISCC
Ti-6Al-4V	1775F 0.5HR FC TO 1200F. 1200F 0.5HR AC. 1200F 3HR ARGON QUENCH	PLATE							X
	1825F 1HR AC	PLATE							X
	1825F 1HR AC. 1350F 2HRS AC						X		
	1810F 1HR WQ. 1100F 8HRS AC 2000F. 0.5HR. AC	FORGING PLATE	X				X		X
Ti-6Al-2V-3Al	STA REAGED AT 1100F 6HR	PLATE							
	1475F 1.5 HR. WQ. 1000F 8 HR. AC	EXTRUSION							
Ti-6	STA-1740F 1 HR. AC. 1000F 8HR. AC	PLATE							X
	1740F 1 HR. AC	PLATE							X
	ALPHA BETA FORGED	FORGING							X

TABLE 4.0.2

PLANE STRAIN FRACTURE TOUGHNESS VALUES OF TITANIUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ HT	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	L-T		T-L		S-L			
				SPECIMEN MEAN THICK *	STD. DEV.	SPECIMEN MEAN THICK *	STD. DEV.	SPECIMEN MEAN THICK *	STD. DEV.		
BETA C	BTA	PLATE	2.50	1.00	44.1	1.4	1.00	43.9	0.6	---	---
BETA III	1325F 925F 8HR	PLATE	0.80	0.75	49.8	1.2	---	---	---	---	---
TI-6	STA-1740F 1 HR. AC. 1000F 8HR. AC	PLATE	0.62	0.62	59.3	1.9	---	---	---	---	---
	1740F 1 HR. AC	PLATE	0.62	0.63	61.6	1.6	---	---	---	---	---
TI-6AL-4V	AS FORGED-MA ALPHA-BETA FORGED. HILL ANNEALED	FORGING	2.25	---	---	---	1.00	39.4	2.7	---	---
	ANNEALED	FORGING	3.00	1.50	84.4	1.8	1.49	83.4	9.9	---	---
		EXTRUSION	4.00	---	---	---	1.63	93.3	2.3	---	---
		BILLET	6.00	1.25	79.6	9.6	---	---	---	---	---
	ANNEALED 1000F 2 HR. AC	BILLET	2.50	1.25	50.9	0.6	---	---	---	---	
	ANNEALED 1300F 4 HR. AC	FORGING	2.50	0.75	58.1	1.2	0.75	62.2	3.0	0.75	68.1
	ANNEALED 1375F 3HR. AC	PLATE	2.75	1.25	60.4	5.5	---	---	---	---	---
	AS RECEIVED	FORGED BAR	1.00-3.90	0.96	57.1	10.4	0.90	54.9	10.8	---	---
	B FORGED BETA FORGED REHEATED TO 1950F DRAWN TO SIZE. ANNEALED 1500F	FORGED BAR	2.25	---	---	---	1.00	42.6	4.3	---	---

* MINIMUM SPECIMEN THICKNESS (IN.)

TABLE 4.0.2 (Cont)

PLANE STRAIN FRACTURE TOUGHNESS VALUES OF TITANIUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ HT	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	K1C (KSI SQRT(IN))		L-T		T-L		S-L		
				SPECIMEN THICK *	MEAN STD. DEV.	SPECIMEN THICK *	MEAN STD. DEV.	SPECIMEN THICK *	MEAN STD. DEV.			
TI-6AL-4V	B FORGED-NA BETA FORGED, MILL ANNEALED 1300F 2 HR, AC	FORGING	2.00	1.00	70.6	4.9	1.00	71.0	0.4	1.00	73.9	2.9
				3.00	1.50	94.9	4.8	---	---	---	---	---
	BETA PROCESSED MILL ANNEALED	PLATE	3.00	1.00-3.50	0.98	68.2	9.7	0.68	64.2	11.8	---	---
				1.00-1.50	1.24	55.6	1.3	---	---	---	---	---
	DIFFUSION BOND ANNEALED	BILLET	1.00-3.50	1.00-2.00	---	---	---	---	---	---	---	---
				1.23-2.00	---	---	---	1.25	100.6	6.8	---	---
	MILL ANNEAL	PLATE	1.00-1.50	1.90-4.00	1.47	83.5	3.1	1.50	87.5	4.1	---	---
				2.00	1.00	47.7	2.9	1.00	49.5	3.9	1.00	43.6
	MILL ANNEALED 1300F 2 HR, AC	EXTRUSION	2.30	1.00-2.50	1.25	84.0	3.4	---	---	---	---	---
				1.20-6.70	1.25	83.6	5.5	1.25	83.9	6.9	1.25	88.9
	RECRYSTALLIZE ANNEAL	FORGING	1.40	0.62	---	---	---	0.63	42.6	2.0	---	---
				1.50	1.25	73.9	4.2	1.28	81.2	5.8	---	---
STA 1700F 6 HR, AC, 1400F 6 HR, AC	PLATE	3.00	---	---	---	---	2.00	79.3	4.9	---	---	
			1.50	---	---	---	1.50	71.5	2.1	---	---	
1750F 1 HR, WQ, 1000F 4 HR	FORGING	1.50	---	---	---	---	---	---	---	---	---	
			1.50	1.50	71.8	3.2	1.50	71.6	1.3	---	---	
1750F 1HR.FC TO 1100F, AC	PLATE	1.50	---	---	---	---	---	---	---	---	---	
			1.50	0.63	41.4	2.3	---	---	---	---		
1750F 2HR, WQ, 1000F 2HR, AC, 1300F 2HR, AC, STA	PLATE	0.62	---	---	---	---	---	---	---	---	---	
			---	---	---	---	---	---	---	---		

* MINIMUM SPECIMEN THICKNESS (IN.).

TABLE 4.0.2 (Cont)

PLANE STRAIN FRACTURE TOUGHNESS VALUES OF TITANIUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ HT	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	K1C (KSI SQRT(IN))							
				L-T	T-L	B-L					
				SPECIMEN MEAN THICK *	SPECIMEN MEAN STD. DEV.	SPECIMEN MEAN STD. DEV.	SPECIMEN MEAN THICK *	SPECIMEN MEAN STD. DEV.	SPECIMEN MEAN THICK *	SPECIMEN MEAN STD. DEV.	
TI-6AL-4V(ELI)	ANNEALED	FORGING	3.00	2.00	83.5	1.3	2.01	84.3	0.4	---	---
	RECRYSTALLIZE ANNEAL	PLATE	3.00	2.00	76.1	4.0	2.00	76.8	0.7	---	---
TI-6AL-6V-2SN	BETA ANNEAL 1810F 1 HR. ARGON COOL	PLATE	0.50	---	---	---	0.45	94.3	2.0	---	---
	BETA ANNEAL & STDA-1800F 0.5HR.AC.1975F 0.5HR.WB.1050F 8 HR.AC	PLATE	0.62	0.63	50.1	1.8	---	---	---	---	---
	DUPLEX ANNEAL	PLATE	0.50	---	---	---	0.50	65.1	2.0	---	---
	MILL ANNEALED	PLATE	0.50-1.00	---	---	---	0.49	59.0	5.2	---	---
	FORGING	FORGING	3.80	1.00	98.6	2.7	---	---	---	---	---
	BILLET	BILLET	2.20	1.24	52.3	6.4	---	---	---	---	---
	MILL ANNEALED 1000F 2 HR.AC	BILLET	2.20	1.29	97.1	2.2	---	---	---	---	---
	STA-1600F 0.5HR.WB.1000F 6 HR.AC	FORGING	3.80	1.01	30.8	0.7	---	---	---	---	---
	STA-1679F 0.25 HR.WB. 1100F 4 HR	PLATE	1.25	---	---	---	0.50	34.1	3.8	---	---
	STDA-1700F 1 HR.WB.1400F 1 HR.AC	PLATE	0.38	0.38	42.9	1.2	0.38	46.1	3.1	---	---
	BILLET	BILLET	12.00	1.02	62.8	6.9	1.02	97.0	3.7	---	---
	STA-1600F 1150F 5 HR	PLATE	1.00	1.00	54.0	1.0	0.99	93.9	1.0	---	---

* MINIMUM SPECIMEN THICKNESS (IN).

TABLE 4.0.2 (Cont)

PLANE STRAIN FRACTURE TOUGHNESS VALUES OF TITANIUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ HT	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	K _{IC} (KSI SQRT(IN))					
				L-T	T-L	S-L			
				SPECIMEN MEAN THICK *	STD. DEV.	SPECIMEN MEAN THICK *	STD. DEV.	SPECIMEN MEAN THICK *	STD. DEV.
Ti6Al4V2Sn(ELI)	1600F 1 HR. W8.	PLATE	1.00	0.29	29.8	0.5			
	1050F 4 HR. AC								
	1650F 1 HR. W8.	PLATE	1.00	0.29	34.0	3.5			

* MINIMUM SPECIMEN THICKNESS (IN.).

TABLE 4.0.3

PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS OF
TITANIUM ALLOYS (WITH BUCKLING CONSTRAINTS)

Alloy	Condition/Mt	Test Temp. (°F)	Specimen Orient	Specimen Width (in.)	Yield Strength (ksi)	K_{IC}^0 (ksi/in)		
						Specimen Thickness (in.) = 0.020	0.040	0.050
Ti-6Al-2.5Sn	Annealed	-423	L-T	3.0	203	116.8/4.5 (5)		
				6.0	203	109.4/6.6 (9)		
				12.0	203	104.2/4.0 (8)		
				16.0	203	97.3/9.6 (2)		
			T-L	12.0	210	107.7/16.0 (2)	147.6/28.9 (2)	
Ti-6Al-4V	NA	R. T.	L-T	24.0	136			196.4/19.9 (6)
				8.0	163			159.4/7.5 (3)
Ti-6Al-4V (ELI)	Annealed	R. T.	L-T	18.0	136			161.6/6.3 (5)
Ti-6Al-1Mo-1V	D. A.	R. T.	L-T	12.0	136			220.5/15.8(4)
				20.0	134			111.7/15.0(3)

Mean/Standard Deviation (No. of Specimens)

TABLE 4.0.4.1

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR TITANIUM ALLOYS

TEST CONDITIONS:

SPECIMEN ORIENTATION: L-T ENVIRONMENT: LAB AIR AT R.T.
 STRESS RATIO: 0.00-0.10 FREQUENCY: 0.10-90.00KHZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE) FOR DELTA K LEVELS (MSI SQRT(IN)) -		
					2.5	5.0	10.0
TI-3AL-2.5Zr	ANNEALED	SHEET	0.10	30.00	11.6	124.	
	ANNEALED	SHEET	0.10	50.00	11.7		
TI-6-2-4-6	-----	EXTRUSION	0.10	20.00	.619	9.70	
	ANNEALED	BILLET	0.02	10.00-20.00	.270	9.49	
TI-6AL-4V	ANNEALED AT 1375F. 3HR. AC	PLATE	0.02	10.00-20.00	.263	9.70	
	BA	FORGING	0.02	10-20.00		2.99	102.
BETA PROCESSED -HILL ANNEALED		PLATE	0.10	1.00		.917	
	MA	PLATE	0.02	10-30.00	.0193	12.4	
MA	MA	PLATE	0.02	10-30.00		8.92	
	MA	PLATE	0.04	20.00		96.9	
MA	MA	PLATE	0.03	20.00		6.97	
	MA	FORGING	0.02	1.00-30.00		8.18	292.
MA	EXTRUSION	0.10	1.00-20.00		9.30	202.	
TI-6AL-4V(ELI)	ANNEALED	FORGING	0.10	1.00-10.00		12.9	204.
	BA	PLATE	0.10	10.00		10.6	

TABLE 4.0.4.1 (Cont)

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR TITANIUM ALLOYS

TEST CONDITIONS:

SPECIMEN ORIENTATION: L-T ENVIRONMENT: LAB AIR AT R. T.
 STRESS RATIO: 0.00-0.10 FREQUENCY: 0.10-50.00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN)) =				
					2.5	5.0	10.0		
TI-6AL-4V-26N	MA	EXTRUSION	0.02	10-20.00	0440	620	7.73		
					0.02	2.28	13.9	144.	1243.
					0.00	1.00-30.00		67.2	
					0.10	43.00	7.58	246.	
TI-6AL-11MO-1V	MA	SHEET	0.10	43.00	0440	620	7.47		
					0.02	2.28	13.9	144.	1243.
					0.00	1.00-30.00		67.2	
					0.10	43.00	7.58	246.	

TABLE 4.0.4.2

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE
STRESS INTENSITY FACTOR FOR TITANIUM ALLOYS

TEST CONDITIONS:

SPECIMEN
ORIENTATION: T-L

ENVIRONMENT: LAB AIR AT R. T.

STRESS RATIO: 0.02-0.10

FREQUENCY: 0.10-53.30KHZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN)) -					
					2.5	5.0	10.0	20.0	50.0	100.0
TI-6AL-2.5ZN	ANNEALED	SHEET	0.10	30.00-53.30				11.8		
	ANNEALED	SHEET	0.10	30.00				11.9	141.	
TI-6AL-4V	AS WELDED E. B. WELDMENT (WELD ZONE)	WELDMENT	0.10	10.00				5.94		
	AS WELDED E. B. WELDMENT (HEAT AFFECTED ZONE)	WELDMENT	0.10	10.00				6.52		
	BA	FORGING	0.02	10-20.00				2.27	103.	3242.
	MA	EXTRUSION	0.10	3.00-20.00				13.7	281.	
	RA	PLATE	0.10	10.00				21.3		
	STRESS RELIEVED E. B. WELDMENT (HEAT AFFECTED ZONE)	WELDMENT	0.10	10-10.00				14.2	344.	
TI-6AL-4V(ELI)	STRESS RELIEVED E. B. WELDMENT (WELD ZONE)	WELDMENT	0.10	10-10.00				10.1		
	ANNEALED	FORGING	0.10	1.00-20.00				11.9	171.	
	RA	PLATE	0.10	1.00-10.00				7.75	240.	

TABLE 4.0.4.3

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR TITANIUM ALLOYS

TEST CONDITIONS:

SPECIMEN ORIENTATION: C-R

ENVIRONMENT: LAB AIR AT R. T.

STRESS RATIO: 0.03-0.10

FREQUENCY: 0.16-30.00HZ

FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
FOR DELTA K LEVELS (KSI SQRT(IN)) =
2.5 5.0 10.0 20.0 50.0 100.0

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN)) =
TI-6-2-4-2	1790F 1HR AC.	FORGING	0.10	.16	10.3
	1100F 8HRS AC				
TI-6-2-4-6	1690F 2HRS AC.	FORGING	0.10	30.00	.985
	1550F 2HRS OS.				
	1100F 8HRS AC				
TI-6AL-4V	1775F 1HR WQ.	DISK	0.05	.33-10.00	152.
	1675F 1HR WQ.				
	1000F 4HRS AC.				
	900F 3HR				
TI-6AL-4V	1775F 1HR WQ.	DISK	0.03	.33-0.50	1.0
	1675F 1HR WQ.				
	1000F-1200F 2-8HRS AC				
TI-6AL-1MD-IV	1830F 1HR WQ. 1100F 8HRS AC	FORGING	0.10	30.00	.107 1.50

TABLE 4.0.5 (Cont)
STRESS CORROSION CRACKING THRESHOLD DATA FOR TITANIUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/HT	PRODUCT FORM	SPECIMEN ORIENTATION	ENVIRONMENTS				K _{ISCC} (Ksi $\sqrt{\text{in.}}$)		FIELD CLEANING SOLVENT
				INDUSTRIAL ATMOSPHERE	SEACOAST ATMOSPHERE	SUMP TANK WATER	JP-4 FUEL	3.5% NaCl	SHOP CLEANING SOLVENT	
Ti-8Al-1Mo-IV	Mill Annealed	P	L-S T-S					20.0 39.4(5)		
	Mill Annealed									
	1435F 8HR FC	P	T-S					21.0		
	Vacuum Annealed	P	T-L					24.3(3)		
	1520 1HR WQ	P	T-L					21.4		
	1675F 1HR AC, 1075F 8HR AC, 1000F 2HR AC	P	T-L					26.4		
	1700F 1HR AC 1200F 2HR WQ	P	T-S					28.0		
	1825F 1HR AC	P	T-S					23.0		
	2000F 0.5 HR AC	P	T-L					47.3		

TABLE 4.1.3.1

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.1.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		BETA TI			
CONDITION: BETA STABILIZED					
K MAX (KSI*IN**1/2)	A:	DA/DT (10**--3 IN/HOUR)			
		B:	C:	D:	
		E= 3.5% NAACL			
K MAX MIN	A: B: C: D:				
200.00					
K MAX MAX	A: B: C: D:				
ROOT MEAN SQUARE PERCENT ERROR		0.00			

CONDITION/HT: BETA STABILIZED
 FORM: 0.1" TH SHEET
 SPECIMEN TYPE:
 ORIENTATION:
 YIELD STRENGTH: 136.0 KSI
 ULT. STRENGTH:

SPECIMEN THK: 0.180"
 SPECIMEN WIDTH: 8.000"
 CRACK LENGTH (A₀):
 K_{ISCC}: 68.00 KSI (SQRT IN)
 REFERENCES: 77458

TITAN.
 ALLOY
 BETA TI

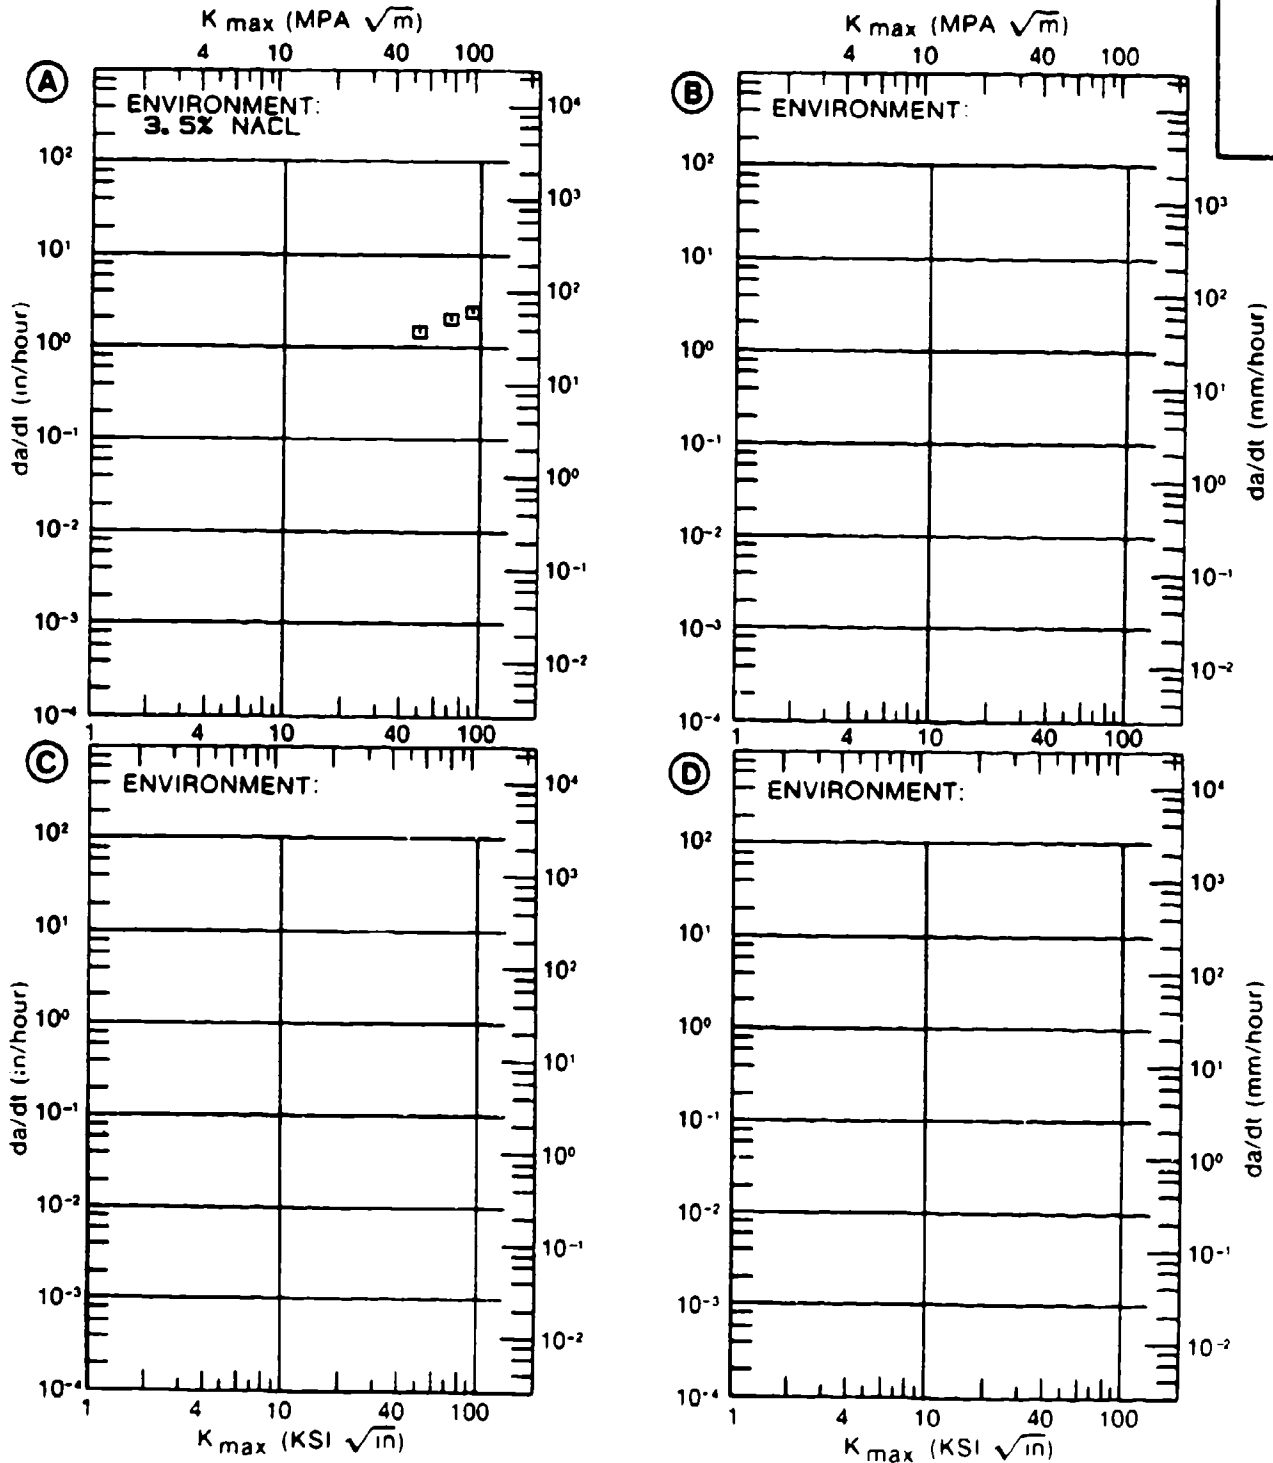


Figure 4.1.3.1

TABLE 4.1.3.2

CONDITION	--PROJCT-- FORM	THICK (IN)	TEMP (F)	TEST SPEC OR STR	YIELD (KSI)	TITANIUM		BETA		K(ISSC)		STAN DEV	TEST TIME (MIN)	DATE REFER
						ENVIRONMENT	WIDTH (IN)	SPECIMEN THICK (IN)	DESIGN (IN)	CRACK LENGTH (IN)	K(ISSC)			
BETA STAR	S	0.16	R.T.	L-S	136.0	3.9	PCT NaCl	8.000	0.140	CNT	72.00	< 68.00*	20	1969 77456
1745F W3	S	---	R.T.	---	---	---	.6M KCL, +1000MV	---	---	SENT	100.00	44.00	---	1970 82651
1745F W3	S	---	R.T.	---	---	---	.6M KCL, -1000MV	---	---	SENT	100.00	55.00*	---	1970 82651
1745F W3	S	---	R.T.	---	---	---	.6M KCL, 0 MV	---	---	SENT	100.00	32.00	---	1970 82651
1745F W3	S	---	R.T.	---	---	---	.6M KCL, +500MV	---	---	SENT	100.00	34.00	---	1970 82651
1745F W3	S	---	R.T.	---	---	---	.6M KCL, -500MV	---	---	SENT	100.00	22.00	---	1970 82651
1745F W3	S	---	R.T.	---	---	---	.6M KCL, -750MV	---	---	SENT	100.00	28.00	---	1970 82651
1745F W3, +1095F 61HR	S	---	R.T.	---	---	---	.6M KCL, -500MV	---	---	SENT	32.00	22.00	---	1970 82651
1745F W3, +1095F 1000HR	S	---	R.T.	---	---	---	.6M KCL, -500MV	---	---	SENT	8.00	8.00	---	1970 82651
1745F W3, +1095F 16HR	S	---	R.T.	---	---	---	.6M KCL, -500MV	---	---	SENT	60.00	26.00	---	1970 82651
1745F W3, +1095F 250HR	S	---	R.T.	---	---	---	.6M KCL, -500MV	---	---	SENT	22.00	16.00	---	1970 82651
1745F W3, +1095F 300HR	S	---	R.T.	---	---	---	.6M KCL, -500MV	---	---	SENT	8.00	8.00	---	1970 82651

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(K(ISSC/TYS)SQUARED

TABLE 4.2.2.1

CONDITION	TITANIUM										K (IC)	K (IC) STAN MEAN DEV (KSI*SQRT IN)	DATE	REFER
	--PRODUCT--		TEST SPECIMEN		SPECIMEN		CRACK		2.5*					
	FORM	THICK (IN)	THICK (F)	ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	LENGTH (IN)	K (IC)/TYS**2 (IN)				
STA	P	2.50	65	I-T	---	1.993	1.001	CT	1.107	0.07	31.40	1974	88575 (1)	
		2.50			---	2.002	1.000	CT	1.076	0.06	30.50	1974	88575 (1)	
		2.50			---	1.988	0.978	CT	1.044	0.07	31.30	1974	88575 (1)	
											31.1/		0.3	
STA	P	2.50	R.T.	I-T	180.0	1.973	0.979	CT	1.042	0.15	43.80	1974	88575	
		2.50			180.0	1.974	1.004	CT	1.074	0.14	42.80	1974	88575	
		2.50			180.0	1.976	1.001	CT	1.070	0.16	45.60	1974	88575	
STA	P	2.50	R.T.	T-L	180.0	1.996	1.002	CT	1.047	0.14	43.40	1974	88575	
		2.50			180.0	1.995	1.001	CT	1.041	0.15	44.30	1974	88575	

NOTES
(1) TYS APPROX 190

TABLE 4.2.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.2.3.1 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: TITANIUM BETA-C
CONDITION: STA
ENVIRONMENT: R. T. , DRY AIR

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	R=+0.10	R=+0.50		
DELTA K A: 5.37	.164			
MIN B:				
C:				
D:				
6.00	.301			
7.00	.624			
8.00	1.07			
9.00	1.62			
10.00	2.26			
13.00	4.56			
16.00	7.40			
20.00	12.3			
25.00	21.6			
30.00	37.1			
35.00	63.5			
40.00	110.			
DELTA K A: 41.22	125.			
MAX B:				
C:				
D:				
ROOT MEAN SQUARE	22.03	0.00		
PERCENT ERROR				

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	
RATIO	0.8-1.25	1
SUMMARY	1.25-2.0	1
(NP/NA)	>2.0	

CONDITION/HT: STA
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 8.00 HZ
 ENVIRONMENT: R. T., DRY AIR

YIELD STRENGTH: 187.7 KSI
 ULT. STRENGTH: 193.5 KSI
 SPECIMEN THK: 0.125- 0.126"
 SPECIMEN WIDTH: 8.002- 8.028"
 REFERENCES: 98575

TITAN.
 ALLOY

BETA-C

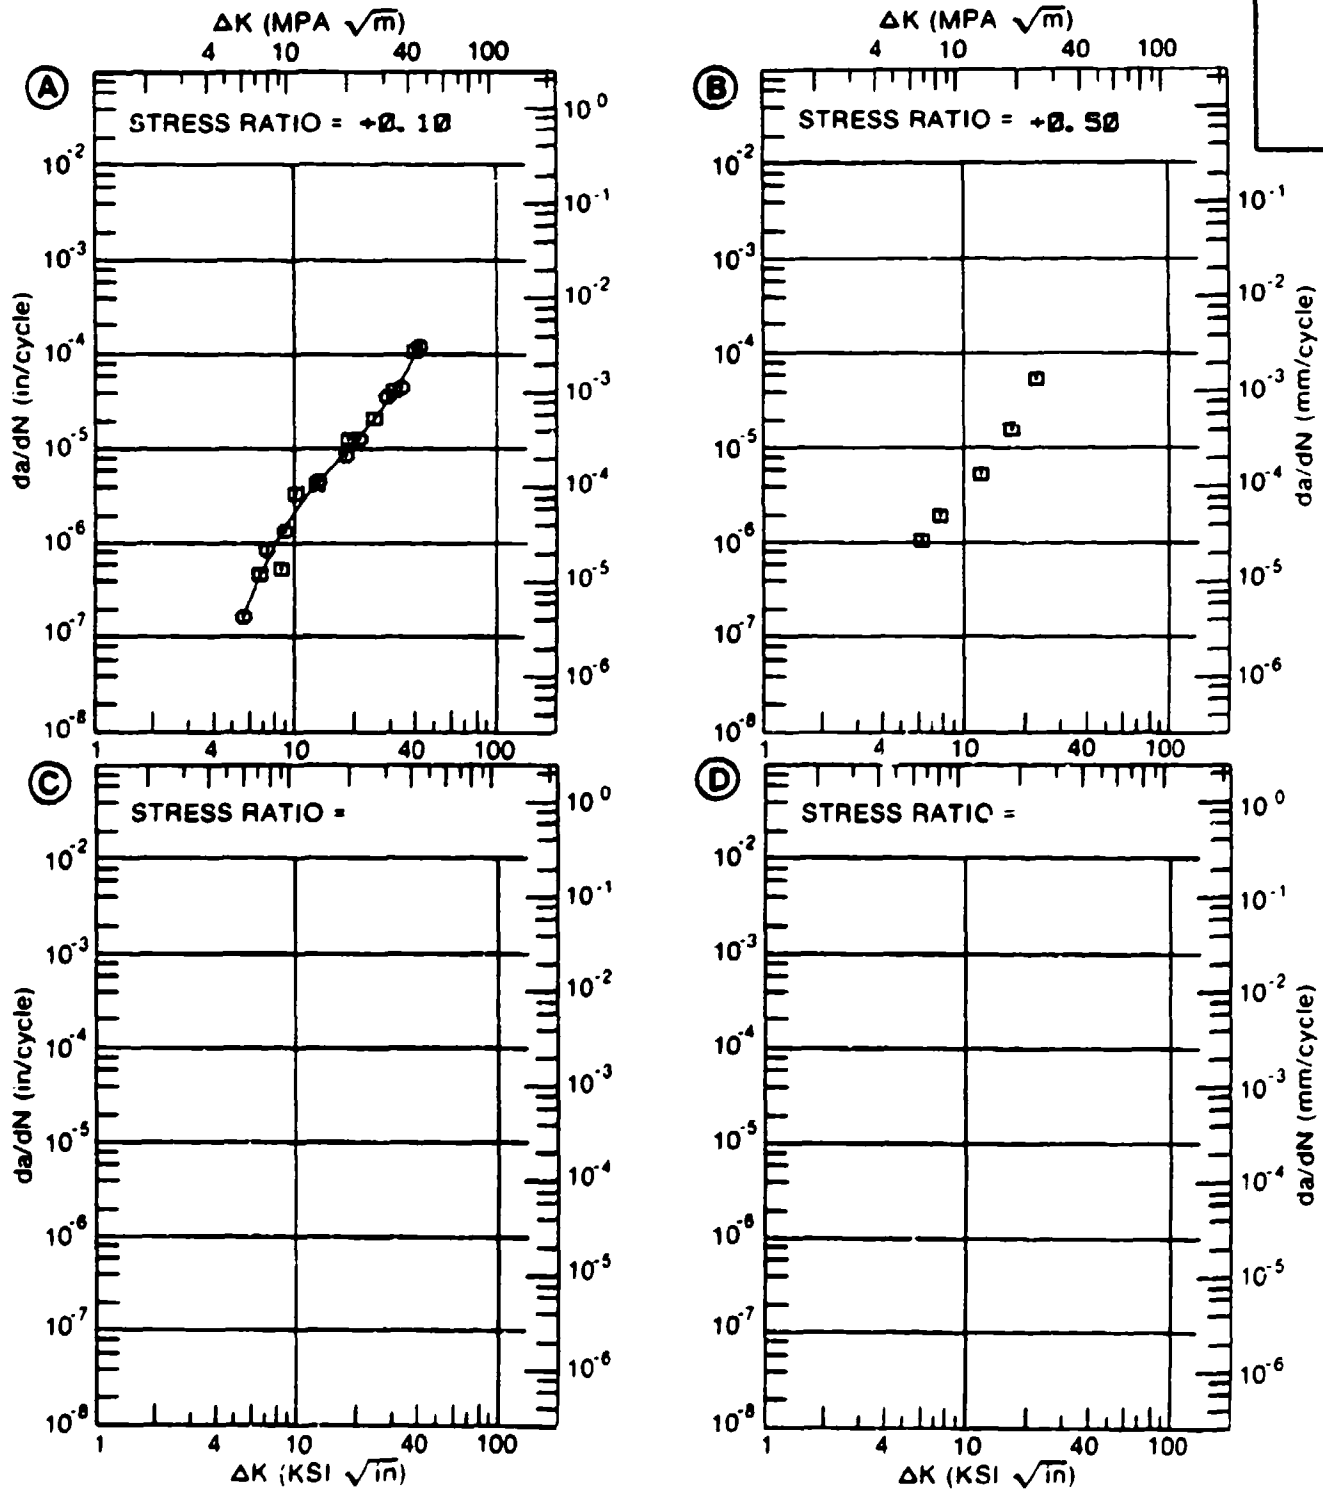


Figure 4.2.3.1

TABLE 4.2.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.2.3.2 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM BETA-C
CONDITION: STA
ENVIRONMENT: R. T. , S. T. W.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K	A: 6.58	.805			
MIN	B:				
	C:				
	D:				
	7.00	1.03			
	8.00	1.67			
	9.00	2.45			
	10.00	3.35			
	13.00	6.72			
	16.00	11.3			
	20.00	20.2			
	25.00	39.4			
	30.00	75.1			
	35.00	143.			
	40.00	271.			
DELTA K	A: 42.90	394.			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 29.18 0.00
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 4
SUMMARY 1.25-2.0 1
(NP/NA) >2.0

CONDITION/HT: STA
 FORM: Ø. 12- Ø. 13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: Ø. 1Ø- 1.ØØ HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 1Ø7.7 KSI
 ULT. STRENGTH: 183.5 KSI
 SPECIMEN THK: Ø. 116- Ø. 127"
 SPECIMEN WIDTH: 6.ØØ2- 6.Ø23"
 REFERENCES: ØØ575

TITAN.
 ALLOY

BETA-C

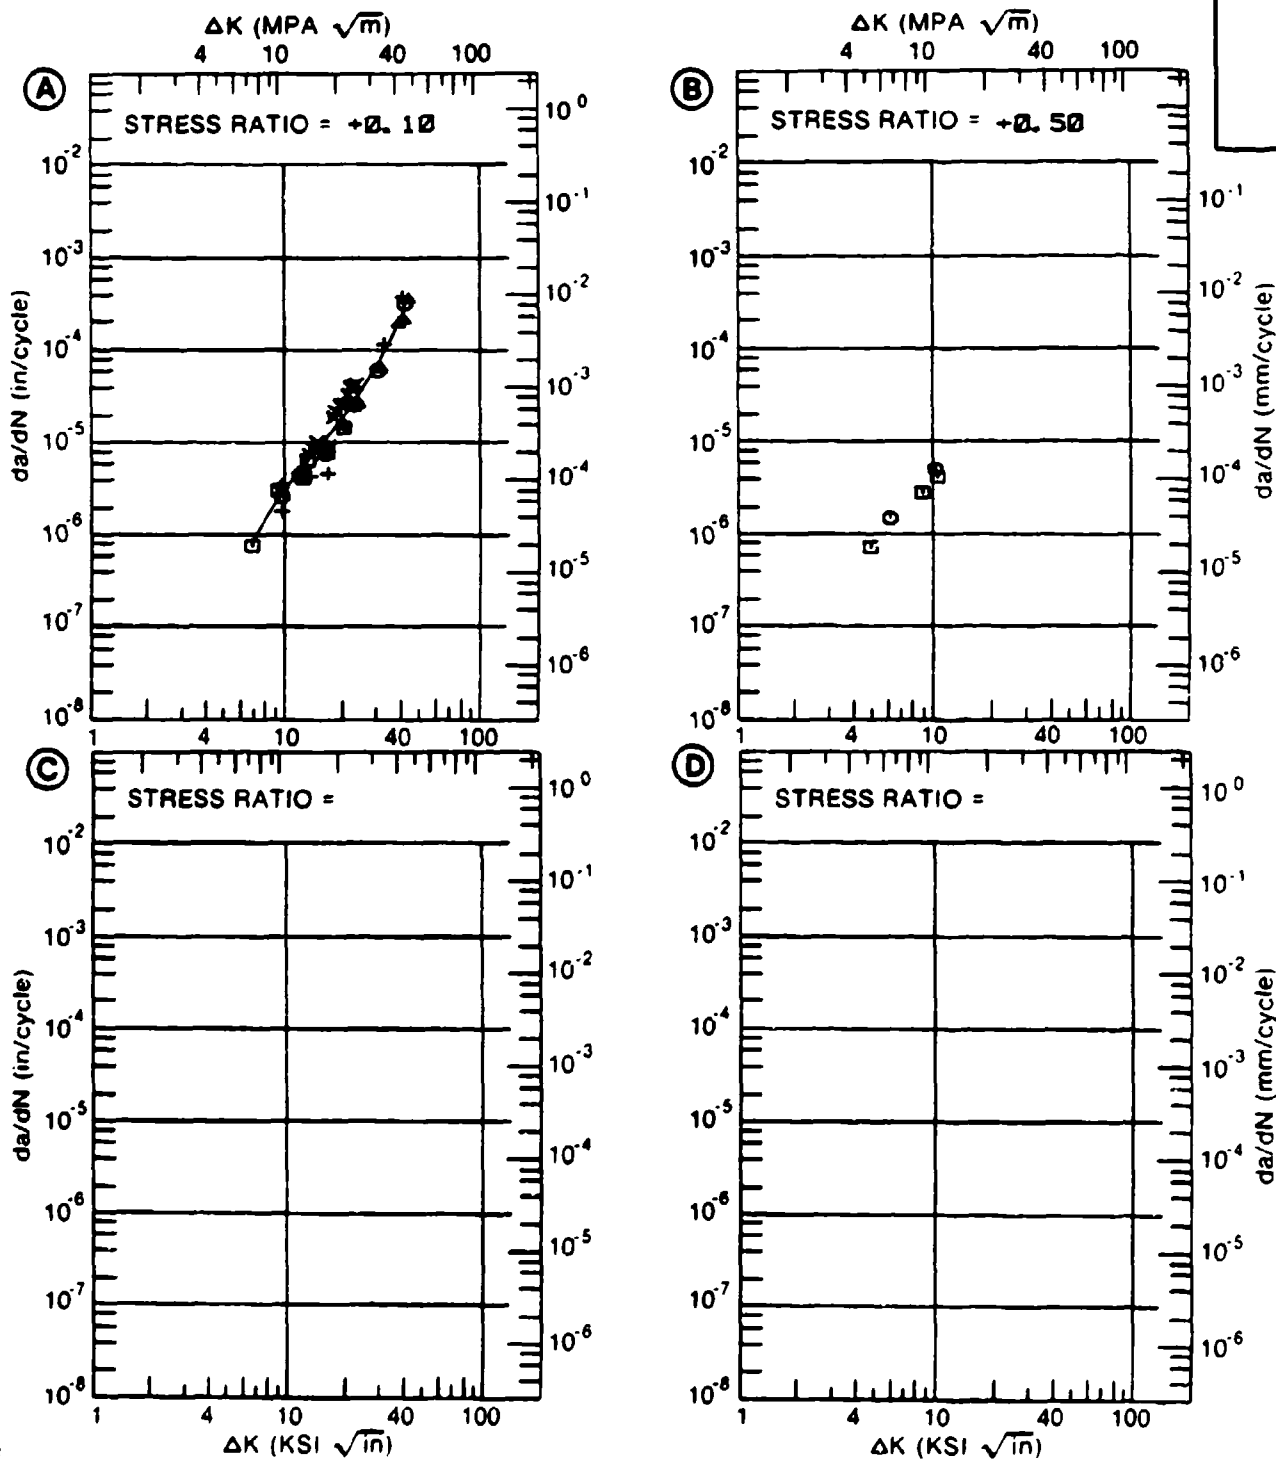


Figure 4.2.3.2

TABLE 4.2.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.2.3.3 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		BETA-C			
CONDITION: STA					
ENVIRONMENT: R. T. , S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A: B: C: D:	:	:	:	:
	200.00	:	:	:	:
DELTA K MAX	A: B: C: D:	:	:	:	:
ROOT MEAN SQUARE PERCENT ERROR		0.00			
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY (NP/NA)	1.25-2.0 >2.0				

CONDITION/HT: STA
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 167.7 KSI
 ULT. STRENGTH: 183.5 KSI
 SPECIMEN THK: 0.127"
 SPECIMEN WIDTH: 6.009"
 REFERENCES: 89575

TITAN.
 ALLOY

BETA-C

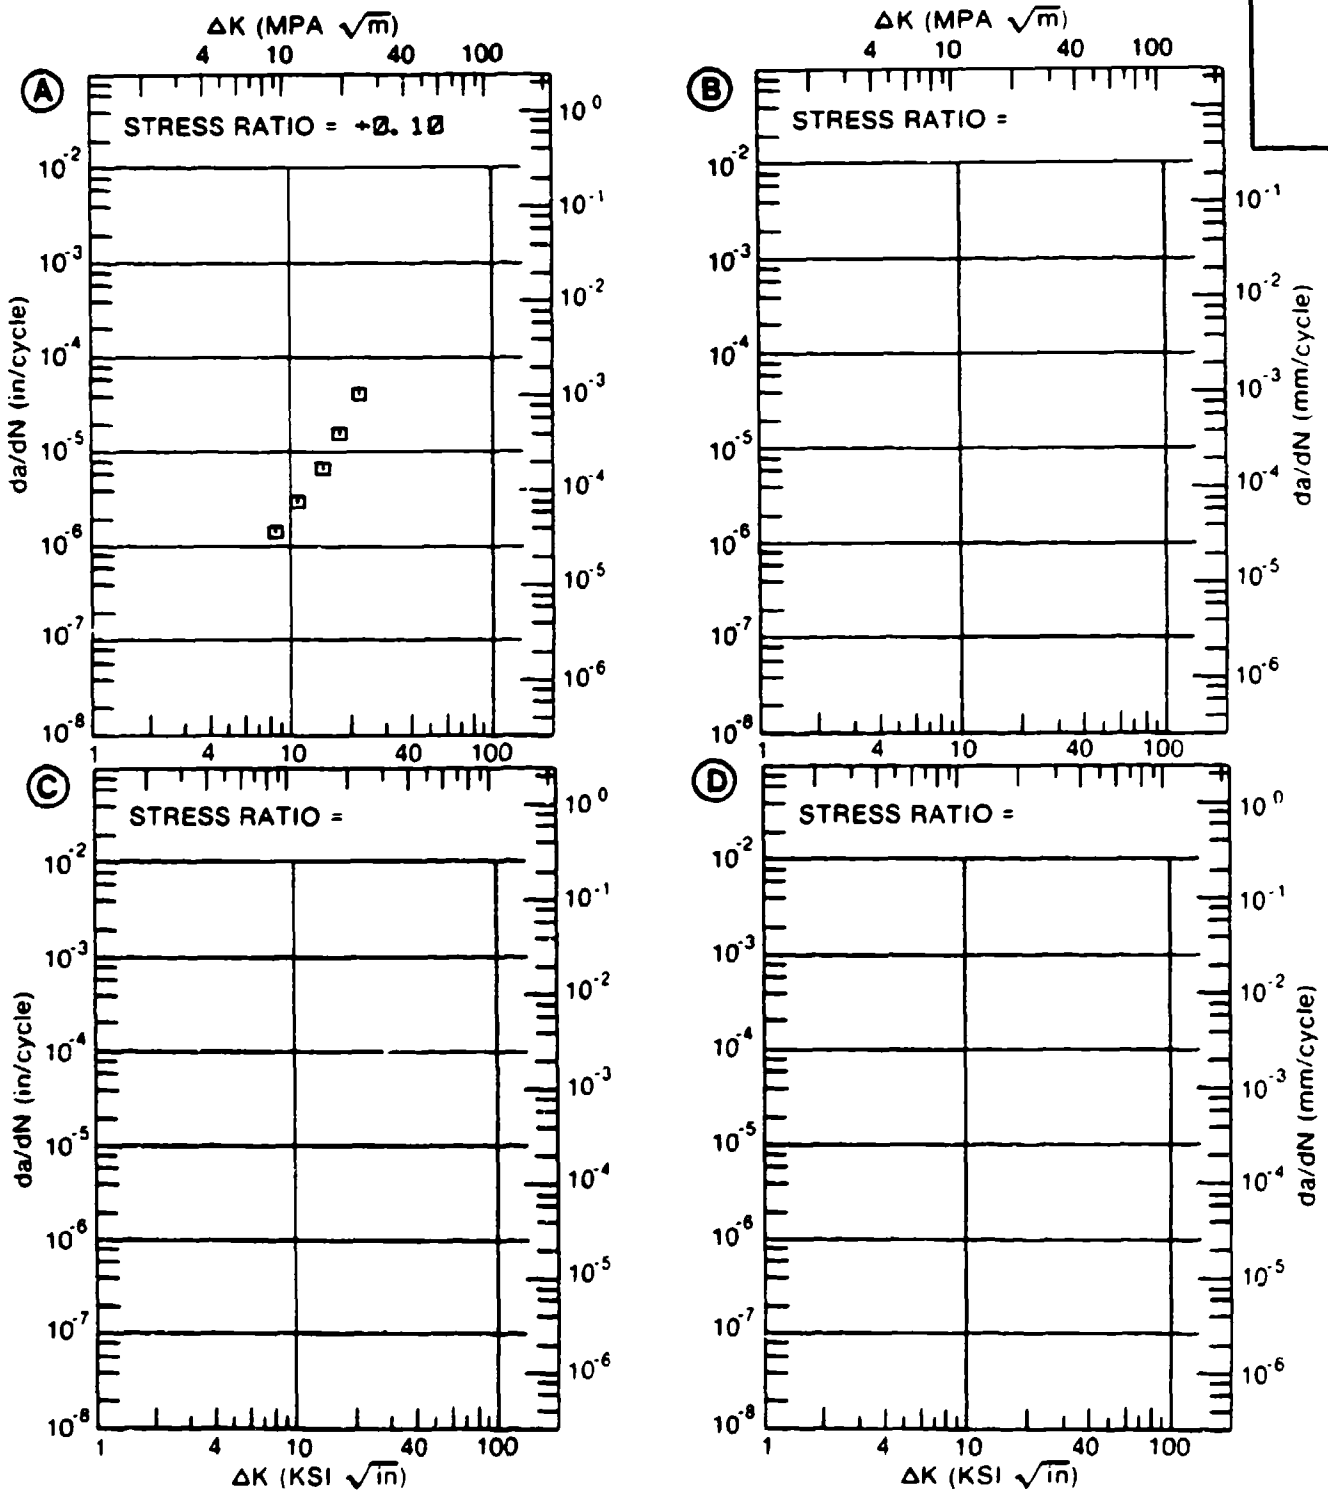


Figure 4.2.3.3

TABLE 4.3.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM BETA III

TEST CONDITIONSSPECIMEN
ORIENTATION T-LENVIRONMENT AIR
AT 175 F

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
STA	PLATE	0.10	0.10-10.00								110
STA. F B WELDMENT (HEAT AFFECTED ZONE)	WELDMENT	0.10	0.10-10.00								97.2

TABLE 4.3.2.1

CONDITION	TITANIUM		BETA III		K(IIC)		K(IIC) STAN K(IIC) MEAN DEV (KSI*SQRT IN)	DATE	REFER					
	YIELD (KSI)	THICKNESS (IN)	WIDTH (IN)	THICKNESS (IN)	CRACK LENGTH (IN)	2.5* (K(IIC)/TVS)**2 (IN)								
STA-1325F WG.1045F BWR	P	1.00	R.T.	T-L	2.000	0.991	CT	0.917	0.17	42.20	1973	83144		
STA-1325F WG.1045F BWR	P	1.00	R.T.	T-L	2.000	0.996	CT	0.930	0.35	76.30	1973	88144		
STA-1325F WG.1045F B WR	P	1.00	R.T.	T-L	2.000	1.005	CT	0.977	0.67	83.70	1973	88144		
1325F 20HR.W0 925F DWR	P	0.80	R.T.	L-T	1.504	0.750	CT	0.763	0.17	48.40	1974	91793		
		0.60			1.503	0.750	CT	0.795	0.18	50.50	1974	91793		
		0.80			1.502	0.750	CT	0.775	0.18	50.40	49.8/	1.2	1974	91793
1325F 0.5 HR. WG.950F DWR.AC	E	3.00	R.T.	C-R	1.459	0.750	CT	0.773	0.24	55.20	1973	87230 (1)		
		3.00			1.479	0.750	CT	0.789	0.26	56.80	1973	87230 (1)		
		3.00			1.499	0.751	CT	0.790	0.23	53.20	1973	87230 (1)		
										59.1/	1.8			

NOTES
(1) ALPHA PRECIPITATE IN BETA MATRIX
STRAIGHTNESS OF CRACK FRONT MAY NOT MEET ASTM E399-72 REQUIREMENTS

TABLE 4.3.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.3.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		BETA III			
CONDITION: STA					
DELTA K (KSI*IN**1/2)		DA/DN (10**6 IN. /CYCLE)			
		A	B	C	D
		E=- 65F	E=+ 175F		
		AIR	AIR		
DELTA K	A: 26.74	28.9			
MIN	B: 20.02		10.1		
	C:				
	D:				
	25.00		19.1		
	30.00	34.0	31.8		
	35.00	41.6	47.8		
	40.00	52.2	66.7		
	50.00	100.	110.		
	60.00	260.			
DELTA K	A: 68.42	291.			
MAX	B: 58.85		149.		
	C:				
	D:				
ROOT MEAN SQUARE		23.87	5.19		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: STA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 0.10- 10.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: 88144

TITAN.
 ALLOY
 BETA III

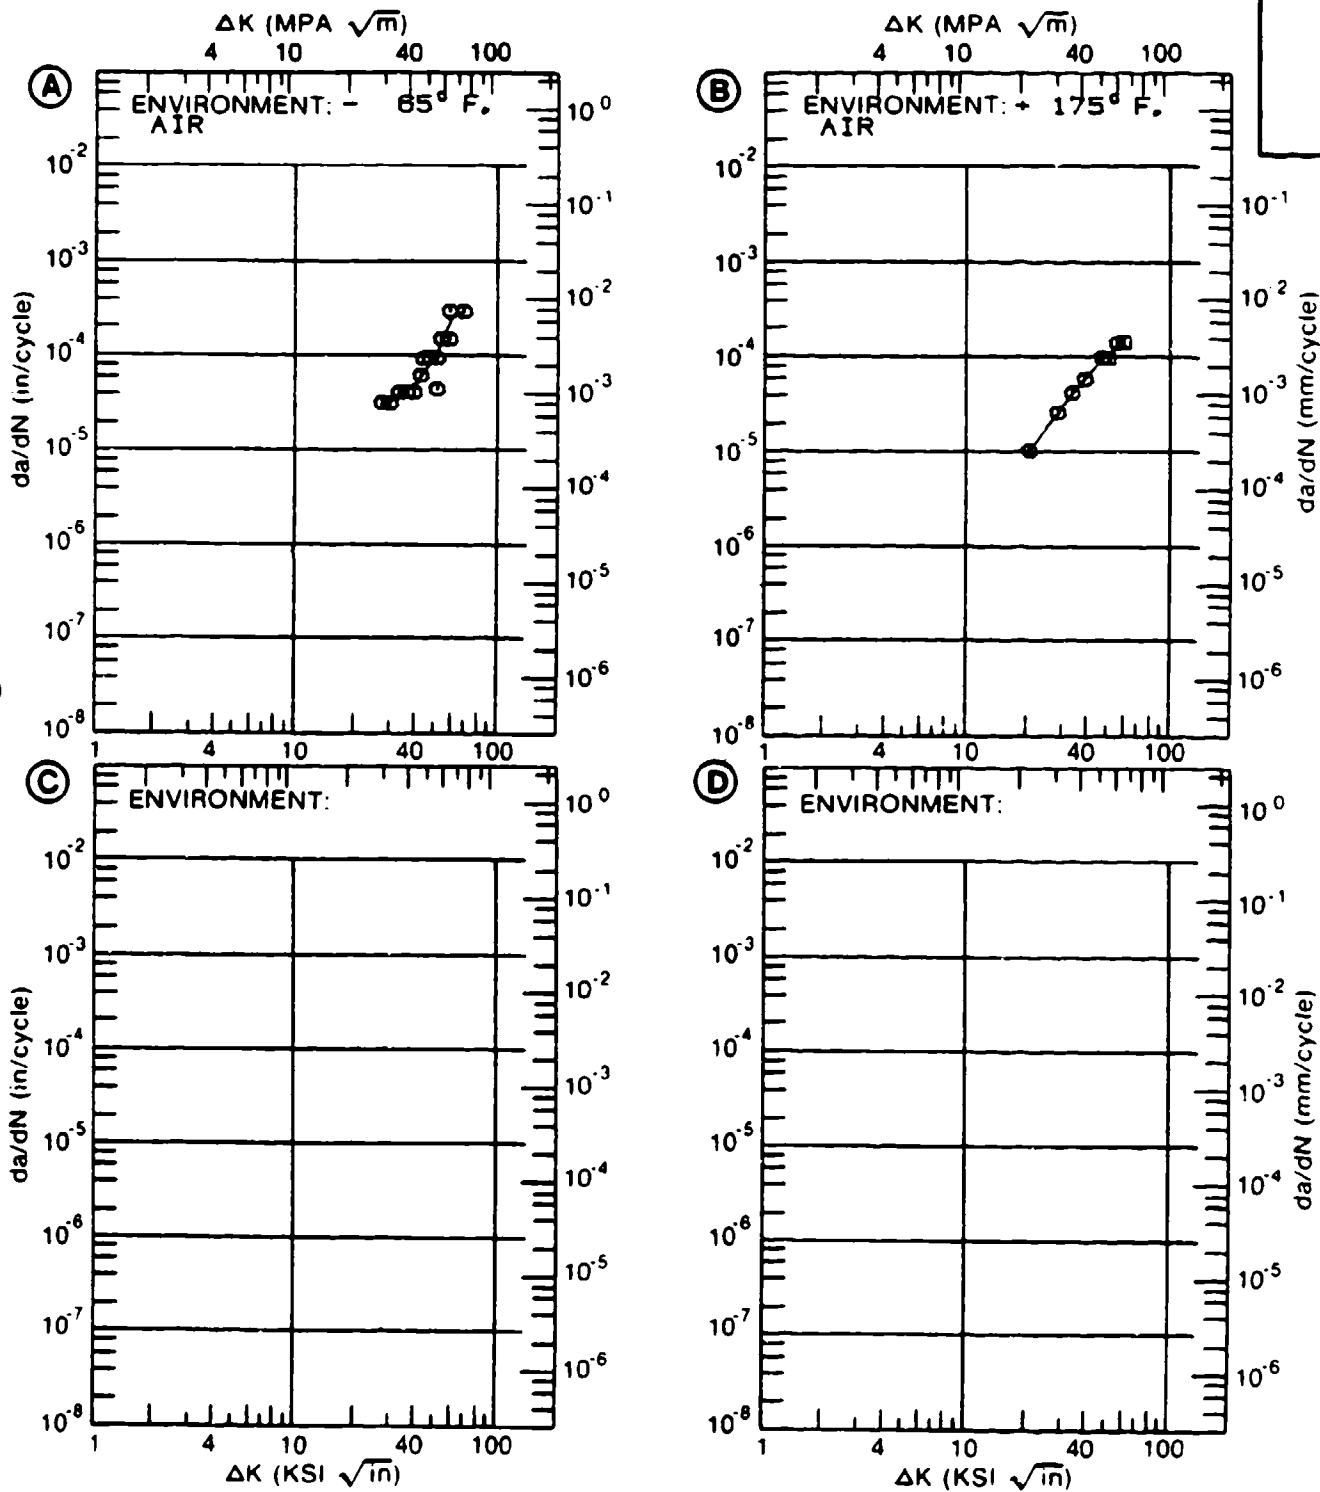


Figure 4.3.3.1

TABLE 4.3.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.3.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		BETA III			
CONDITION: STA. E. B. WELDMENT (WELD ZONE)					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		LAB AIR			
DELTA K MIN	A: B: C: D:				
	200.00				
DELTA K MAX	A: B: C: D:				
ROOT MEAN SQUARE PERCENT ERROR		0.00			
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0				

CONDITION/HT: STA. E. B. WELDMENT (WELD ZONE)

FORM: 1.00" TH WELDMENT

SPECIMEN TYPE: CT

ORIENTATION: T-L

STRESS RATIO: +0.10

FREQUENCY: 10.00 HZ

YIELD STRENGTH:

ULT. STRENGTH:

SPECIMEN THK: 1.000"

SPECIMEN WIDTH: 2.550"

REFERENCES: 88144

TITAN.
ALLOY

BETA III

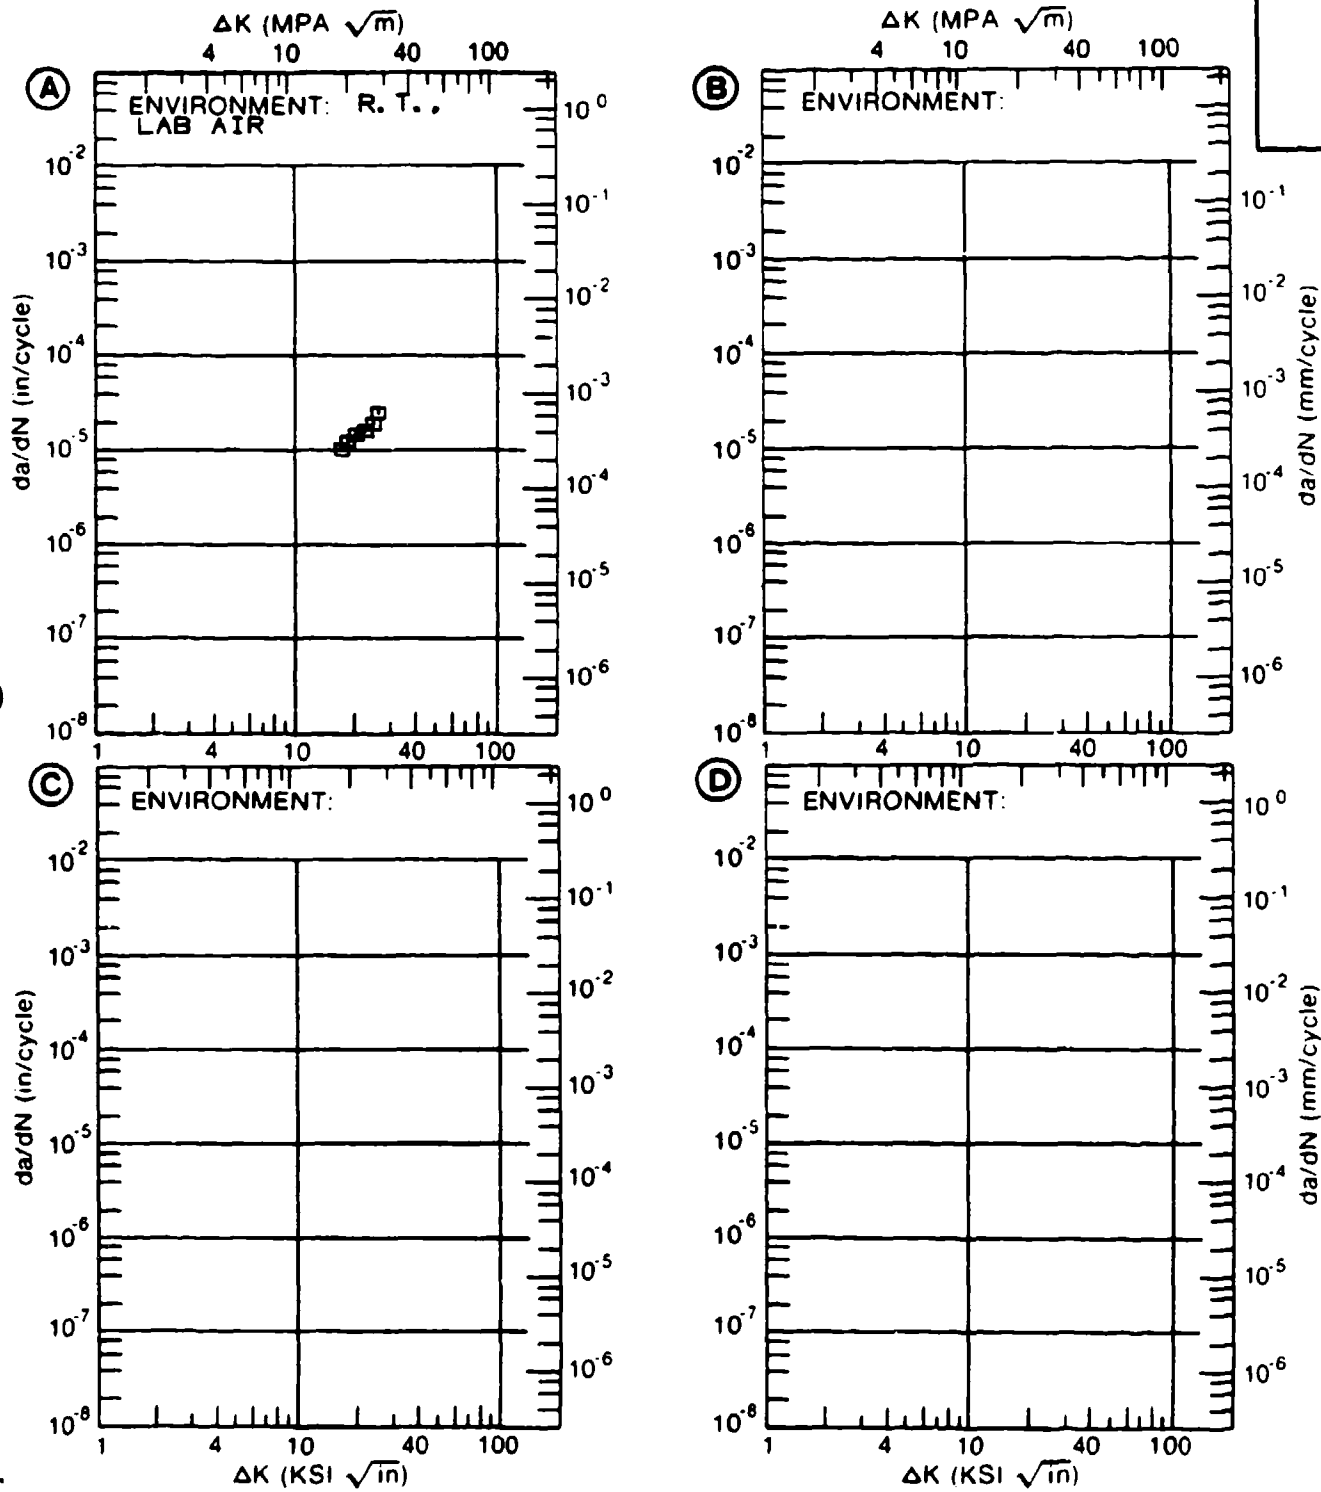


Figure 4.3.3.2

TABLE 4.3.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.3.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		BETA III			
CONDITION: STA, E. B. WELDMENT (HEAT AFFECTED ZONE)					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E=+ 175F			
		: AIR			
DELTA K	A: 24.74	: 12.8			
MIN	B:	:			
	C:	:			
	D:	:			
	25.00	: 13.2			
	30.00	: 23.2			
	35.00	: 35.2			
	40.00	: 50.1			
	50.00	: 97.2			
DELTA K	A: 58.23	: 171.			
MAX	B:	:			
	C:	:			
	D:	:			
ROOT MEAN SQUARE		9.56			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: STA. E.B. WELDMENT (HEAT AFFECTED ZONE)

FORM: 1.00" TH WELDMENT

SPECIMEN TYPE: CT

ORIENTATION: T-L

STRESS RATIO: +0.10

FREQUENCY: 0.10- 10.00 HZ

YIELD STRENGTH:

ULT. STRENGTH:

SPECIMEN THK: 1.000"

SPECIMEN WIDTH: 2.550"

REFERENCES: 08144

TITAN.
ALLOY

BETA III

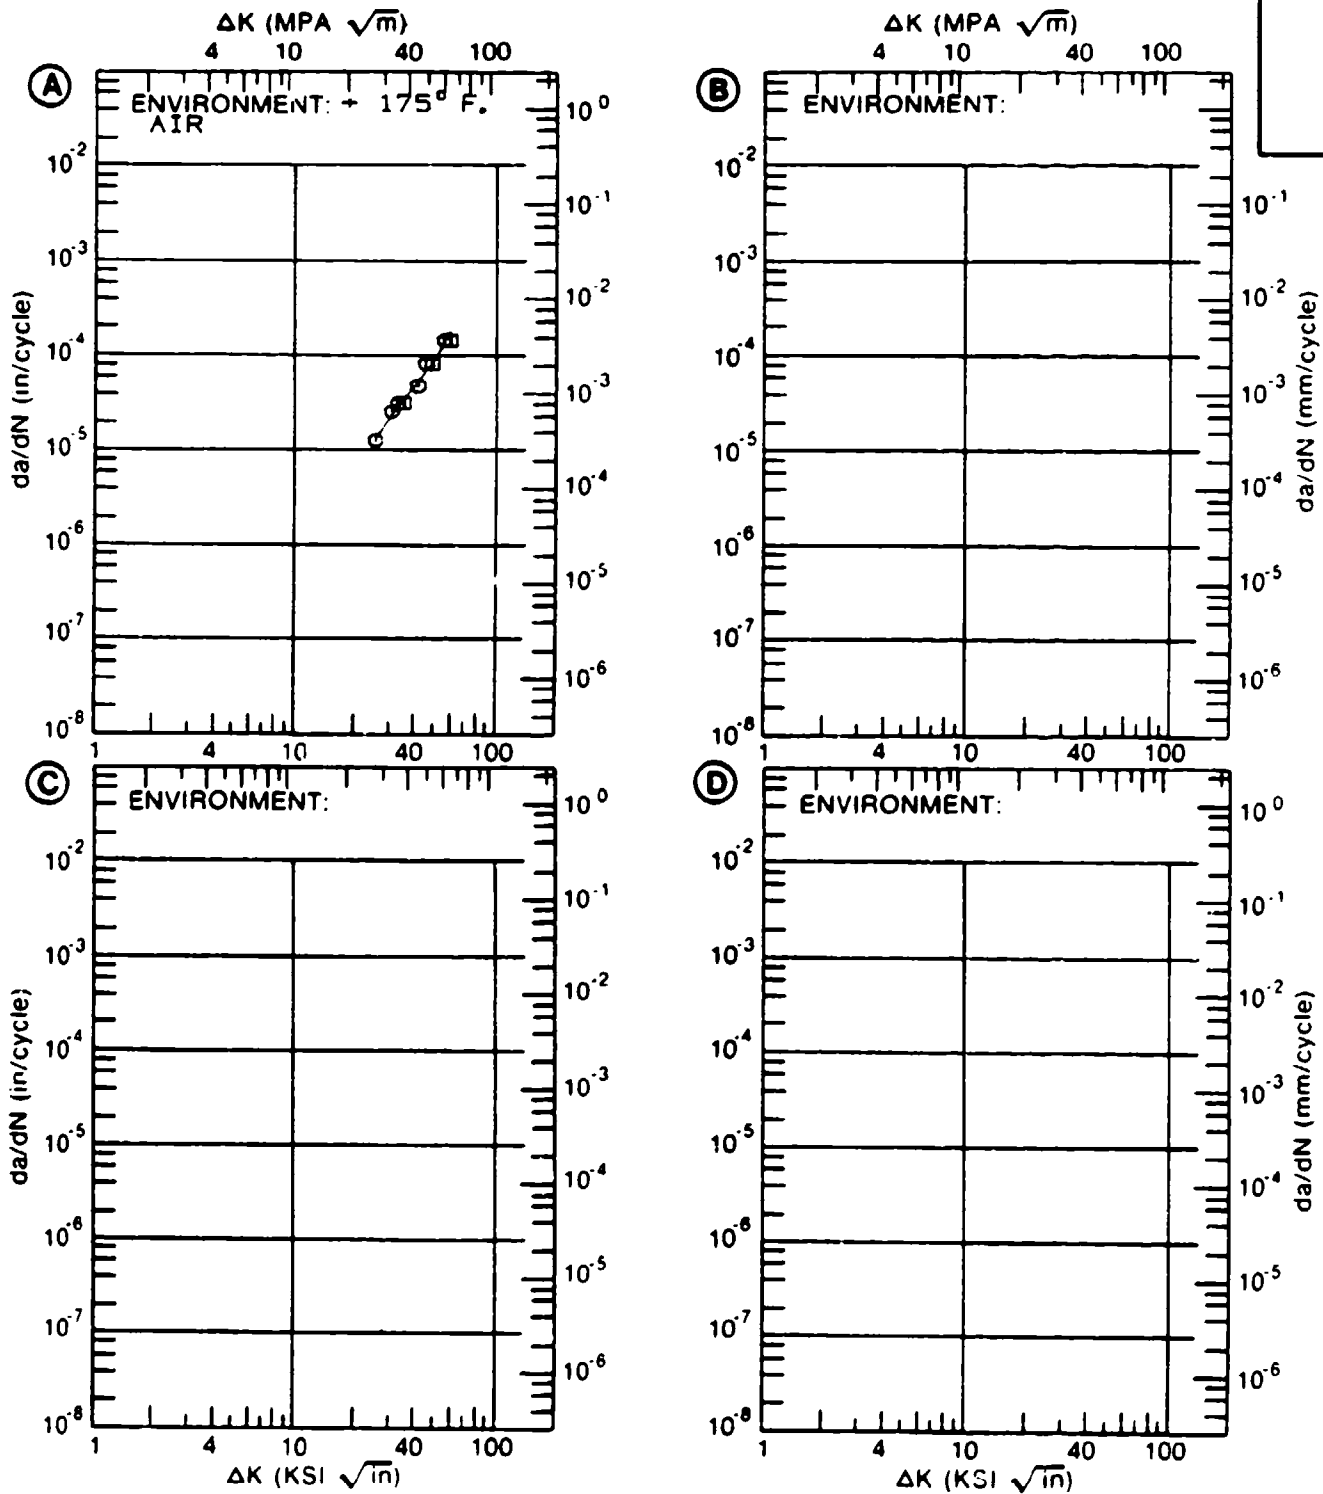


Figure 4.3.3.3

TABLE 4.3.3.4

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.3.3.4 INDICATING EFFECT

OF CONDITION

MATERIAL: TITANIUM		BETA III			
ENVIRONMENT: R. T. , 0.6M KCL					
K MAX (KSI*IN**1/2)		DA/DT (10** ⁻³ IN/HOUR)			
		A	B	C	D
		C= AGED 900F 100HRS	C= AGED 1000F 100HRS	C= AGED 1250F 50HRS	
K MAX MIN	A: 15.50	40051.			
	B: 23.00		11709.		
	C:				
	D:				
	16.00	40305.			
	20.00	41048.			
	25.00	40606.	13521.		
	30.00	40032.	15835.		
35.00	39804.	16116.			
40.00	40045.	15677.			
50.00	41973.	15093.			
60.00		16211.			
70.00		19830.			
K MAX MAX	A: 59.50	45536.			
	B: 80.00		27367.		
	C:				
D:					
ROOT MEAN SQUARE		8.50	6.09	0.00	
PERCENT ERROR					

CONDITION/HT:
 ENVIRONMENT: R. T., 0. 6M KCL
 SPECIMEN TYPE: SENT
 ORIENTATION:
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK:
 SPECIMEN WIDTH:
 CRACK LENGTH (A_0):
 K_{ISCC} :
 REFERENCES: 82851

TITAN.
 ALLOY
 BETA III

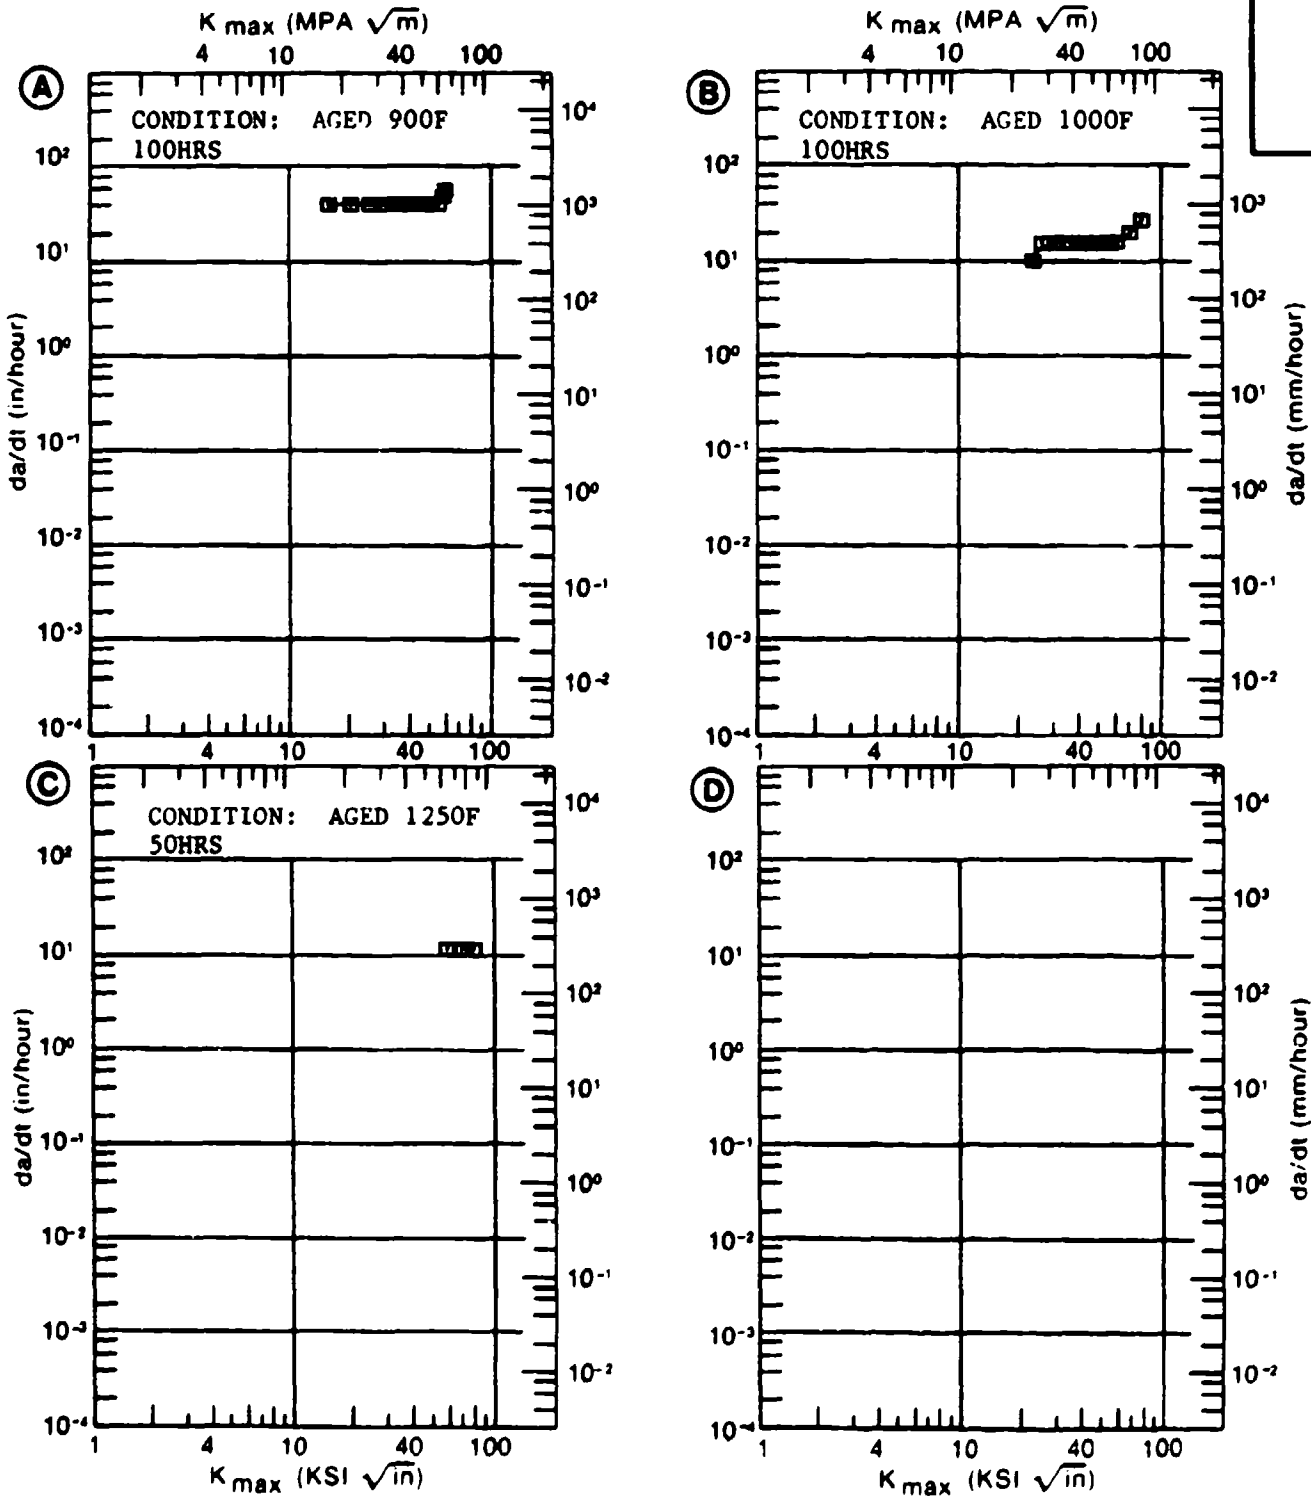


Figure 4.3.3.4

TABLE 4.3.3.5

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.3.3.5 INDICATING EFFECT
OF CONDITION

MATERIAL: TITANIUM		BETA III			
ENVIRONMENT: 0.6M KCL					
K MAX (KSI*IN**1/2)		DA/DT (10**-3 IN/HOUR)			
		A	B	C	D
		C= STA 900F 100HRS	C= STA 900F 8HRS	C= STA 900F 40HRS	
K MAX MIN	A: 15.00	35940.			
	B:				
	C: 25.50			2144.	
	D:				
	16.00	36148.			
	20.00	36335.			
	25.00	36035.			
	30.00	35746.			3216.
	35.00	35668.			4046.
	40.00	35843.			4457.
50.00	36930.			4444.	
K MAX MAX	A: 56.00	38016.			
	B:				
	C: 55.00			4234.	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		7.67	0.00	6.13	

CONDITION/HT:
 ENVIRONMENT: 0.8M KCL
 SPECIMEN TYPE: SENT
 ORIENTATION:
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK:
 SPECIMEN WIDTH:
 CRACK LENGTH (A_0):
 K_{ISCC} :
 REFERENCES: 82851

TITAN.
 ALLOY

BETA II

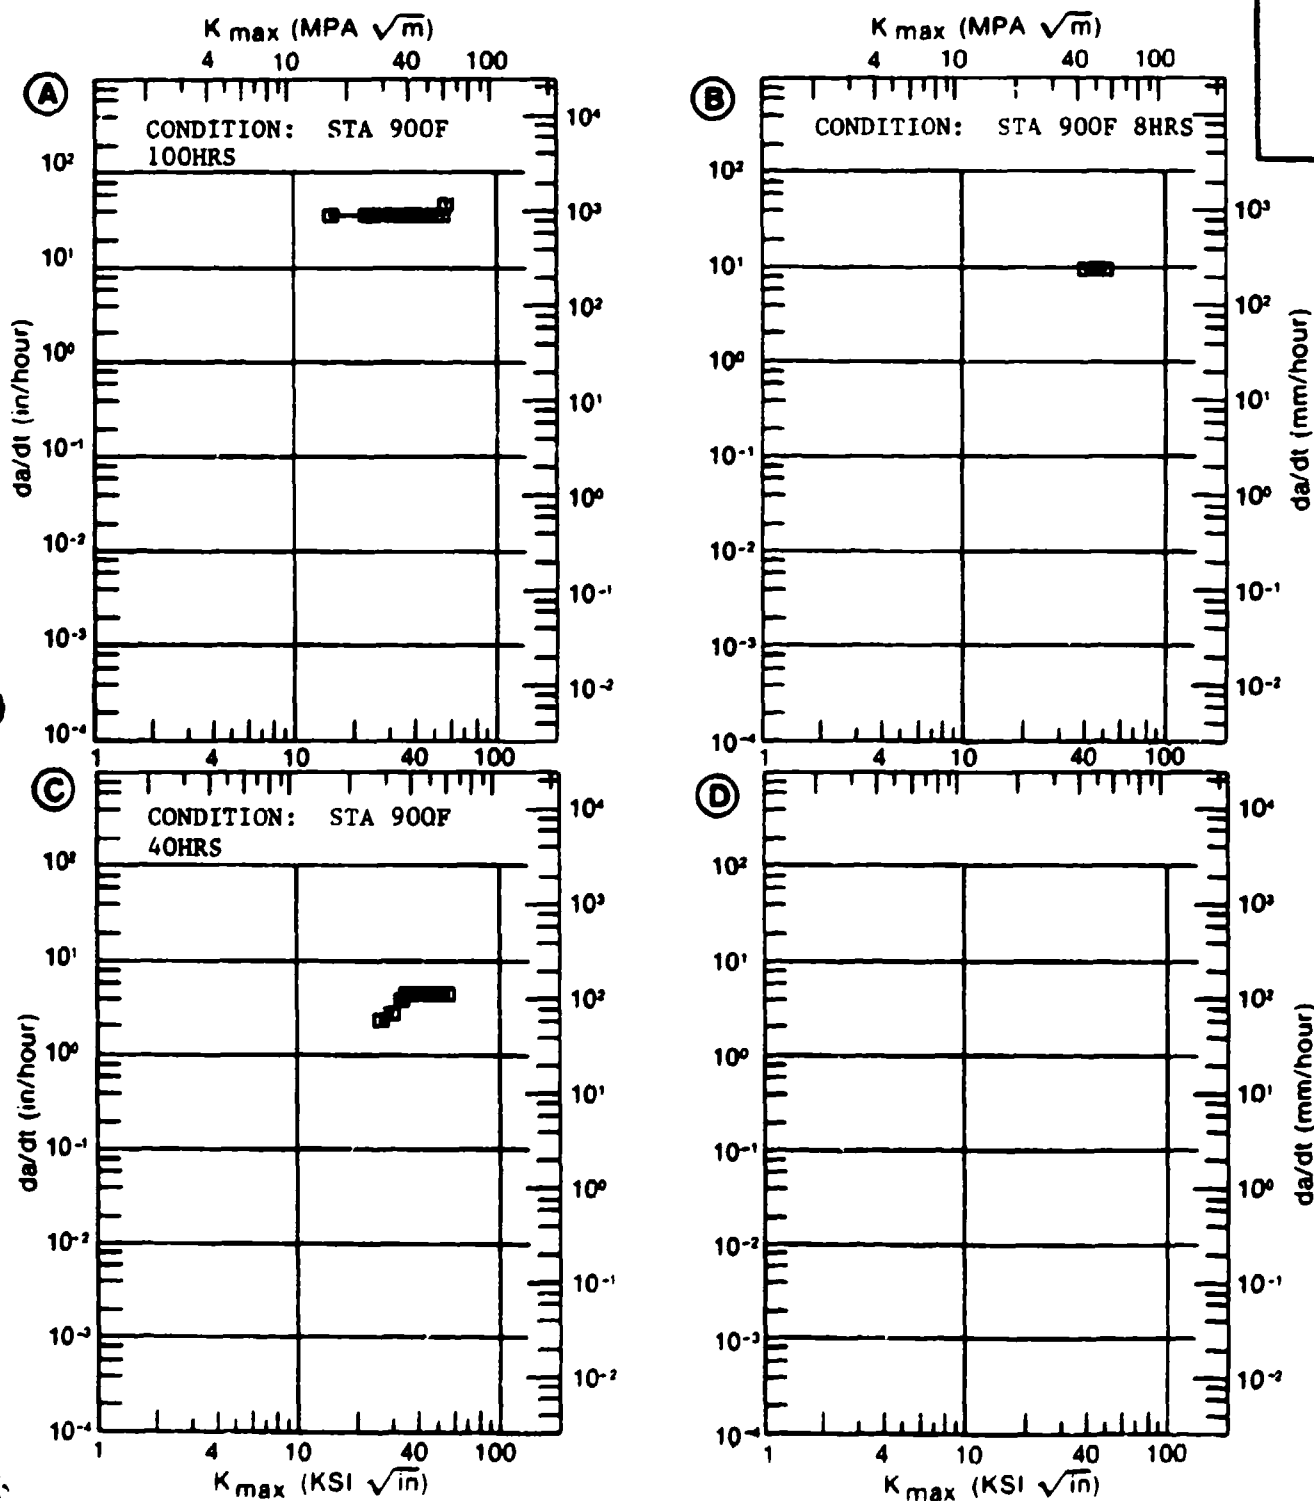


Figure 4.3.3.5

TABLE 4.3.3.6

CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST TEMP (F)	SPEC YIELD OR STR (KSI)	ENVIRONMENT	TITANIUM		BETA III		K(ISSC)		MEAN	STAN DEV	TEST TIME (MIN)	DATE	PEFER
						WIDTH (IN)	THICKNESS (IN)	DESIGN (IN)	LENGTH (IN)	CRACK K(ISSC)						
BETA STAB +AGED 900F 1HR	S	---	R. T.	---	.6M KCL, -1500RV	---	SENT	---	SENT	---	65.00	55.00*	---	---	1970	82651
BETA STAB +AGED 900F 1HR	S	---	R. T.	---	.6M KCL, -1000RV	---	BENT	---	BENT	---	65.00	28.00	---	---	1970	82651
BETA STAB +AGED 900F 1HR	S	---	R. T.	---	.6M KCL, +1000RV	---	SENT	---	SENT	---	65.00	25.00	---	---	1970	82651
BETA STAB +AGED 900F 1HR	S	---	R. T.	---	.6M KCL, 0MV	---	BENT	---	BENT	---	65.00	21.00	---	---	1970	82651
BETA STAB +AGED 900F 1HR	S	---	R. T.	---	.6M KCL, +900RV	---	SENT	---	SENT	---	65.00	24.00	---	---	1970	82651
BETA STAB +AGED 900F 1HR	S	---	R. T.	---	.6M KCL, -500RV	---	SENT	---	SENT	---	65.00	14.00	---	---	1970	82651
BETA STAB +AGED 900F 1HR	S	---	R. T.	---	.6M KCL, -750RV	---	SENT	---	SENT	---	65.00	16.00	---	---	1970	82651

*NOTE - DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5 (KISSC/TYS) SQUARED

TABLE 4.4.2.1

CONDITION	--PRODUCT-- FORM		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	CORONA 9		K(KIC)	CRACK LENGTH (IN)	2.5 σ K(KIC)/ \sqrt{YB} (IN)	K(KIC) MEAN (KSI \sqrt{BORT} IN)	K(KIC) STAN DEV	DATE	REFER
	THICK (IN)	THICK (IN)			WIDTH (IN)	THICK (IN)							
ALPHA-BETA FORGED & LOW ANGLE	F	2.00	R.T	136.3	M	2.000	0.57	64.84					RIOUS

TABLE 4.5.1.1
 MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
 TITANIUM ALLOY TI-6 AT ROOM TEMPERATURE

CONDITION/MT	MEAN K _{IC} ± STANDARD DEVIATION		PLATE
	(KSI SQRT(IN))	(NUMBER OF SPECIMENS)	
STA-1740F 1 HR. AC. 1000F 6HR. AC	55.3 ± 1.5 (3)	---	PL
1740F 1 HR. AC	61.6 ± 1.6 (3)	---	---

TABLE 4.5.2.1

CONDITION	PRODUCT--		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	TITANIUM		WIDTH (IN)	SPECIMEN--		CRACK LENGTH (IN)	CRACK 2.5* LENGTH (IN)	K(1C) (KSI/RT)	K(1C) MEAN (KSI/RT)	K(1C) STAN DEV (IN)	DATE	REFER
	FORM	THICK (IN)			THICK (IN)	THICK (IN)		M	B							
STA-1740F	P	0.62	R. T.	157.0	2.000	0.624	CT	1.000	0.33	57.00				1974	88186 (1)	
1 HR. AC. 100HF		0.62		157.0	2.000	0.625	CT	1.000	0.30	54.70				1974	88186 (1)	
RMP. AC		0.62		157.0	2.000	0.625	CT	1.000	0.30	54.30			35.3/ 1.5	1974	88186 (1)	

1740F 1 HR. AC	P	0.62	R. T.	148.0	2.000	0.626	CT	1.000	0.44	62.00				1974	88186 (1)	
		0.62		148.0	2.000	0.625	CT	1.000	0.45	62.90				1974	88186 (1)	
		0.62		148.0	2.000	0.625	CT	1.000	0.41	59.60			61.6/ 1.6	1974	88186 (1)	

UNITS
(1) * - GAL - 25N-27R - 2ND - 2CR - 0. 2591

TABLE 4.6.3.1

TITANIUM		TI-4AL-3MO-1V		K(I18CC)									
CONDITION	--PRODUCT-- FORM THICK (IN)	TEST TEMP (F)	SPEC YIELD STR (KSI)	ENVIRONMENT	W	THICK (IN)	DESIGN (IN)	CRACK LENGTH (IN)	K(I18CC) (K(I18CC))	MEAN DEV	BTAN	TEST TIME (MIN)	DATE REFER
	P	0.50	R.T.	L-S	---	3.5	PCT	NACl.	---	117.00	105.00*	---	1969 75386

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.3(KI18CC/TYS)SQUARED

TABLE 4.7.1.1.1

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-SAL-2 35N

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: DRY ARGON AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
ANNEALED	SHEET	0.10	30 00					5.96	94.7		
ANNEALED	SHEET	0.10	50 00					4.77			
ANNEALED	SHEET	0.67	55 00-98 30			0.03	0.27				

TABLE 4.7.1.2
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-5AL-2.5SN

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: LAB AIR
 AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5	5 10 20 30 100
ANNEALED	SHEET	0.10	30.00		11.6 124
ANNEALED	SHEET	0.10	50.00		11.7
ANNEALED	SHEET	0.67	55.00-58.00	0.15	2 13

TABLE 4.7.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-3AL-2.5BN

TEST CONDITIONS

SPECIMEN
ORIENTATION L-TENVIRONMENT DIST H₂O
AT R. T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE)							
				DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100	
ANNEALED	SHEET	0.10	30.00								124
ANNEALED	SHEET	0.10	50.00								11.8
ANNEALED	SHEET	0.67	55.00-59.00				0.25	3.49			

TABLE 4.7.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-5AL-2.5SN

TEST CONDITIONS

SPECIMEN
ORIENTATION L-TENVIRONMENT 3.5% NaCl
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
ANNEALED	SHEET	0.10	30.00		30.2 157
ANNEALED	SHEET	0.10	50.00		23.5
ANNEALED	SHEET	0.67	55.00-58.30		0.29 7.97

TABLE 4.7.1.5
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM T1-SAL-2 35N

TEST CONDITIONS

SPECIMEN ORIENTATION T-L ENVIRONMENT DRY ARGON AT R. T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
ANNEALED	SHEET	0.10	30.00		9.38 114
ANNEALED	SHEET	0.10	50.00-53.30		3.35
ANNEALED	SHEET	0.67	54.20-58.30		0.49

TABLE 4.7.1.6

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM T1-5AL-2.5Sn

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: LAB AIR AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
ANNEALED	SHEET	0.10	30.00		11.9 141
ANNEALED	SHEET	0.10	50.00-33.30		11.8
ANNEALED	SHEET	0.67	54.20-98.30		0.15 3.08

TABLE 4.7.1.7
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM TI-5AL-2.5Sn

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: DIST H2O AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
ANNEALED	SHEET	0.10	30.00					12.5	130	
ANNEALED	SHEET	0.10	50.00-53.30					12.0		
ANNEALED	SHEET	0.67	34.20-38.30			0.36	3.72			

TABLE 4.7.1.8

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-5AL-2.5SN

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT 3.5% NaCl AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATE (MICRO IN/CYCLE)
				2.5	5
				10	20
				50	100
ANNEALED	SHEET	0.10	30.00		176
ANNEALED	SHEET	0.10	50.00-53.30		24.5
ANNEALED	SHEET	0.67	54.20-58.30	0.98	14.6

TABLE 4.7.2.1

TITANIUM		11-3AL-2.5BN		K(C)									
CONDITION	--PRODUCT-- FORM THICK TEMP OR STR (IN) (F) (KSI)	CRACK LENGTH CROSS STRESS				K(C) STAN MEAN DEV (KBI*SQRT IN)	K(C) STAN MEAN DEV (KBI*SQRT IN)	REFER					
		WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL ONSET (KSI)								
		W	B	2A(D) 2A(F)	B(D) S(MAX)	K(APP) STAN MEAN DEV (KBI*SQRT IN)	K(C) STAN MEAN DEV (KBI*SQRT IN)						
BUCKLING OF CRACK EDGES RESTRAINED													
ANNEALED	S	0.02	0.02	423 L-T	203.5	3.000	0.018	0.500	110.10	99.28	111.85	1967	68968
		0.02	0.02		203.5	3.000	0.019	1.040	1.300	69.00	75.34	1967	68968
		0.02	0.02		203.5	3.000	0.019	0.150	0.270	169.40	80.41*	1967	68968
		0.02	0.02		203.5	3.000	0.019	1.000	---	69.30	93.33	1967	68968
		0.02	0.02		203.5	3.000	0.019	1.240	---	72.20	98.91	1967	68968
		0.02	0.02		203.5	3.000	0.019	0.320	0.500	129.90	92.75	1967	68968
		0.02	0.02		203.5	3.000	0.019	0.340	0.670	127.90	94.22	1967	68968
		0.02	0.02		203.5	3.000	0.019	0.120	0.300	181.00	78.64*	1967	68968
		0.02	0.02		203.5	3.000	0.019	0.340	0.810	103.60	97.37	1967	68968
		0.02	0.02		203.5	3.000	0.019	0.510	0.730	107.60	98.06	1967	68968
		0.02	0.02		203.5	3.000	0.020	0.270	0.470	138.90	90.91	1967	68968
		0.02	0.02		203.5	3.000	0.020	1.030	1.280	68.60	94.20	1967	68968
		0.02	0.02		203.5	3.000	0.030	0.130	0.330	172.70	83.96*	1967	68968
ANNEALED	S	0.02	0.02	423 L-T	203.5	6.000	0.018	2.010	2.230	49.00	93.63	1967	68968
		0.02	0.02		203.5	6.000	0.017	2.000	2.390	50.10	93.42	1967	68968
		0.02	0.02		203.5	6.000	0.018	0.490	0.800	103.90	93.29	1967	68968
		0.02	0.02		203.5	6.000	0.018	0.490	0.640	110.50	97.34	1967	68968
		0.02	0.02		203.5	6.000	0.018	0.130	0.250	181.60	82.09*	1967	68968
		0.02	0.02		203.5	6.000	0.019	0.230	0.530	153.30	96.17	1967	68968
		0.02	0.02		203.5	6.000	0.019	0.240	0.640	156.40	96.12	1967	68968
		0.02	0.02		203.5	6.000	0.018	1.000	1.330	73.70	93.98	1967	68968
		0.02	0.02		203.5	6.000	0.018	2.000	2.420	48.80	92.73	1967	68968
		0.02	0.02		203.5	6.000	0.019	0.500	0.720	109.10	97.10	1967	68968
		0.02	0.02		203.5	6.000	0.019	1.020	1.210	71.40	92.02	1967	68968
		0.02	0.02		203.5	6.000	0.019	0.230	0.610	157.20	98.63*	1967	68968
		0.02	0.02		203.5	6.000	0.019	1.000	1.340	74.10	94.47	1967	68968
		0.02	0.02		203.5	6.000	0.018	0.130	0.220	191.90	86.74*	1967	68968
ANNEALED	S	0.02	0.02	423 L-T	203.5	12.000	0.018	0.490	0.620	104.30	91.60	1967	68968
		0.02	0.02		203.5	12.000	0.019	4.000	4.490	35.40	95.35	1967	68968
		0.02	0.02		203.5	12.000	0.019	0.490	0.660	108.60	95.30	1967	68968
		0.02	0.02		203.5	12.000	0.019	0.130	0.380	178.40	80.62*	1967	68968
		0.02	0.02		203.5	12.000	0.018	0.980	1.190	76.00	94.68	1967	68968

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV

TABLE 4.7.2.1 (con't)

TITANIUM		TISAL-2.5SN		K(IC)		CRACK LENGTH		GROSS STRESS		K(APP) STAN		K(IC) STAN				
CONDITION	PROPERTY	TEST SPEC OR THICK (IN)	YIELD STR (KSI)	SPECIMEN		INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) (KSI)	MEAN (KSI)	DEV (KSI)	K(IC) (KSI)	STAN (KSI)	DATE	REFER
				WIDTH (IN)	THICK (IN)											
ANNEALED	S	0.02 - 423 L-T	203.5	12.000	0.019	2.000	2.460	---	51.20	92.34	---	---	103.34	---	1967	68968
		0.02	203.5	12.000	0.018	0.240	0.620	---	154.40	94.82	---	---	126.30*	---	1967	68968
		0.02	203.5	12.000	0.018	0.500	0.690	---	103.60	91.91	---	---	108.08	---	1967	68968
		0.02	203.5	12.000	0.019	1.000	1.170	---	71.30	89.79	---	---	97.23	---	1967	68968
		0.02	203.5	12.000	0.019	2.000	2.410	---	52.10	93.96	93.3/	2.0	103.97	104.2/	4.0	1967
ANNEALED	S	0.02 - 423 L-T	203.5	12.000	0.020	4.000	4.040	---	39.20	105.59	---	---	106.28	---	1967	68968
		0.02	203.5	12.000	0.020	0.120	0.260	---	183.90	79.83*	---	---	117.56*	---	1967	68968
		0.02	203.5	12.000	0.020	0.120	0.310	---	181.10	78.63*	---	---	126.43*	---	1967	68968
		0.02	203.5	12.000	0.021	2.000	2.330	---	51.60	93.06	---	---	101.08	---	1967	68968
		0.02	203.5	12.000	0.020	4.020	4.350	---	35.20	95.12	---	---	100.26	---	1967	68968
ANNEALED	S	0.02	203.5	12.000	0.021	0.240	0.400	---	151.30	92.92	---	---	120.01	---	1967	68968
		0.02	203.5	12.000	0.020	0.240	0.470	---	153.20	94.09	---	---	131.76	---	1967	68968
		0.02	203.5	12.000	0.021	0.990	1.370	---	70.90	88.79	94.9/	5.7	104.85	110.7/12.5	1967	68968
		0.02 - 423 L-T	193.3	15.930	0.016	4.980	5.480	---	32.80	97.69	---	---	103.92	---	1967	68968
		0.02	193.3	15.930	0.019	4.980	5.380	---	29.20	86.97	92.3/	7.6	90.29	97.1/	9.6	1967
ANNEALED	S	0.06 - 423 L-T	228.0	1.000	0.063	0.410	---	---	63.90	57.34	---	---	---	---	1971	80104
		0.06	228.0	1.000	0.064	0.480	---	---	54.60	55.53	---	---	---	---	1971	80104
		0.06	228.0	1.000	0.062	0.080	---	---	131.10	46.66	---	---	---	---	1971	80104
ANNEALED	S	0.06	228.0	1.000	0.064	0.170	---	---	115.50	60.77	55.1/	6.0	---	---	1971	80104
		0.06 - 423 L-T	228.0	2.000	0.063	0.180	---	---	115.10	61.51	---	---	---	---	1971	80104
		0.06	228.0	2.000	0.063	0.140	---	---	123.00	57.86	---	---	---	---	1971	80104
		0.06	228.0	2.000	0.063	0.790	---	---	46.80	57.80	---	---	---	---	1971	80104
ANNEALED	S	0.06	228.0	2.000	0.064	0.420	---	---	78.30	65.39	---	---	---	---	1971	80104
		0.06	228.0	2.000	0.062	0.080	---	---	147.10	52.20	59.0/	4.9	---	---	1971	80104
ANNEALED	S	0.06 - 423 L-T	228.0	3.000	0.064	0.990	---	---	48.50	64.89	---	---	---	---	1971	80104
ANNEALED	S	0.10 - 423 L-T	211.0	1.000	0.113	0.240	---	---	116.90	74.44	---	---	---	---	1971	80104
		0.10	211.0	1.000	0.113	0.360	---	---	90.30	73.90	---	---	---	---	1971	80104
		0.10	211.0	1.000	0.111	0.120	---	---	161.30	70.66*	74.2/	0.4	---	---	1971	80104

BUCKLING OF CRACK EDGES RESTRAINED

*NOTE - NET SECTION STRESS EXCEEDS BOX OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 4.7.2.1 (con't)

CONDITION	TITANIUM		TI-SAL-2.5RN		K(C)		CRACK LENGTH GROSS STRESS		K(IAPP) STAN		K(C) STAN	
	FORM	THICK (IN)	TEST SPEC OR STR (F)	YIELD STR (KSI)	SPECIMEN		INIT (IN)	FINAL (IN)	ONSET (KGI)	MAX (KBI)	K(IAPP) MEAN DEV (KSI*SQRT IN)	K(C) MEAN DEV (KSI*SQRT IN)
					WIDTH (IN)	THICK (IN)						
ANNEALED	0	0.10	- 423 L-T	211.0	0.112	0.130	---	---	138.30	71.72*	---	---
	0	0.10		211.0	0.114	0.270	---	---	119.00	78.38	---	---
	0	0.10		211.0	0.113	0.380	---	---	97.30	76.89	77.6/ 1.1	---
ANNEALED	S	0.10	- 423 L-T	211.0	0.116	1.090	---	---	55.20	76.77	---	---
	0	0.10		211.0	0.116	0.990	---	---	56.30	78.01	77.4/ 0.9	---
ANNEALED	S	0.06	- 420 L-T	228.0	0.064	1.000	---	---	44.90	60.47	---	---
ANNEALED	S	0.02	- 320 L-T	171.2	0.018	3.000	3.400	---	44.60	133.16	139.93	---
ANNEALED	S	0.02	- 320 L-T	171.2	0.020	4.980	3.610	---	44.80	133.11	143.73	---
ANNEALED	S	0.02	R.T. L-T	109.3	0.018	3.060	4.780	---	54.50	163.94	200.71*	---
ANNEALED	S	0.02	R.T. L-T	109.3	0.018	3.070	6.660	---	58.70	176.16	211.86*	---
ANNEALED	S	0.20	R.T. L-T	110.7	0.202	4.950	---	---	68.70	196.87*	---	---
ANNEALED	S	0.02	- 423 T-L	211.8	0.015	1.130	1.590	---	64.70	86.67	96.40	---
	0	0.02		211.8	0.015	0.330	0.710	---	112.40	80.96	83.8/ 4.0 118.96 107.7/16.0	---
ANNEALED	S	0.03	- 423 T-L	207.3	0.036	0.280	1.070	---	129.00	85.38	168.07	---
	0	0.03		207.3	0.036	1.200	1.840	---	73.70	101.81	93.7/11.5 127.14 147.6/28.9	---

*NOTE- NET SECTION STRESS EXCEEDS BOX OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 4.7.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.7.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-5AL-2.5SN			
CONDITION: ANNEALED					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. : DRY ARGON	E= R. T. : LAB AIR	E= R. T. : DIST. H2O	E= R. T. : 3.5% NaCl
DELTA K	A: 16.59 :	2.12			
MIN	B: 17.50 :		8.19		
	C: 16.62 :			7.49	
	D: 17.57 :				16.3
	20.00 :	4.77	11.7	11.8	23.5
	25.00 :	10.0	20.7	20.4	37.5
	30.00 :	17.3	32.5	31.1	50.5
	35.00 :	28.6	47.3	42.4	64.2
	40.00 :			52.7	
DELTA K	A: 38.01 :	38.7			
MAX	B: 37.81 :		57.0		
	C: 42.00 :			56.3	
	D: 38.00 :				73.6
ROOT MEAN SQUARE		4.48	2.10	7.50	4.46
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	2	2	2	2

CONDITION/HT: ANNEALED
 FORM: 0.08" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 50.00 HZ

YIELD STRENGTH: 122.3 KSI
 ULT. STRENGTH: 139.9 KSI
 SPECIMEN THK: 0.083- 0.084"
 SPECIMEN WIDTH: 2.754- 2.758"
 REFERENCES: 88911

TITAN.
 ALLOY

TI-5AL-
 2.5SN

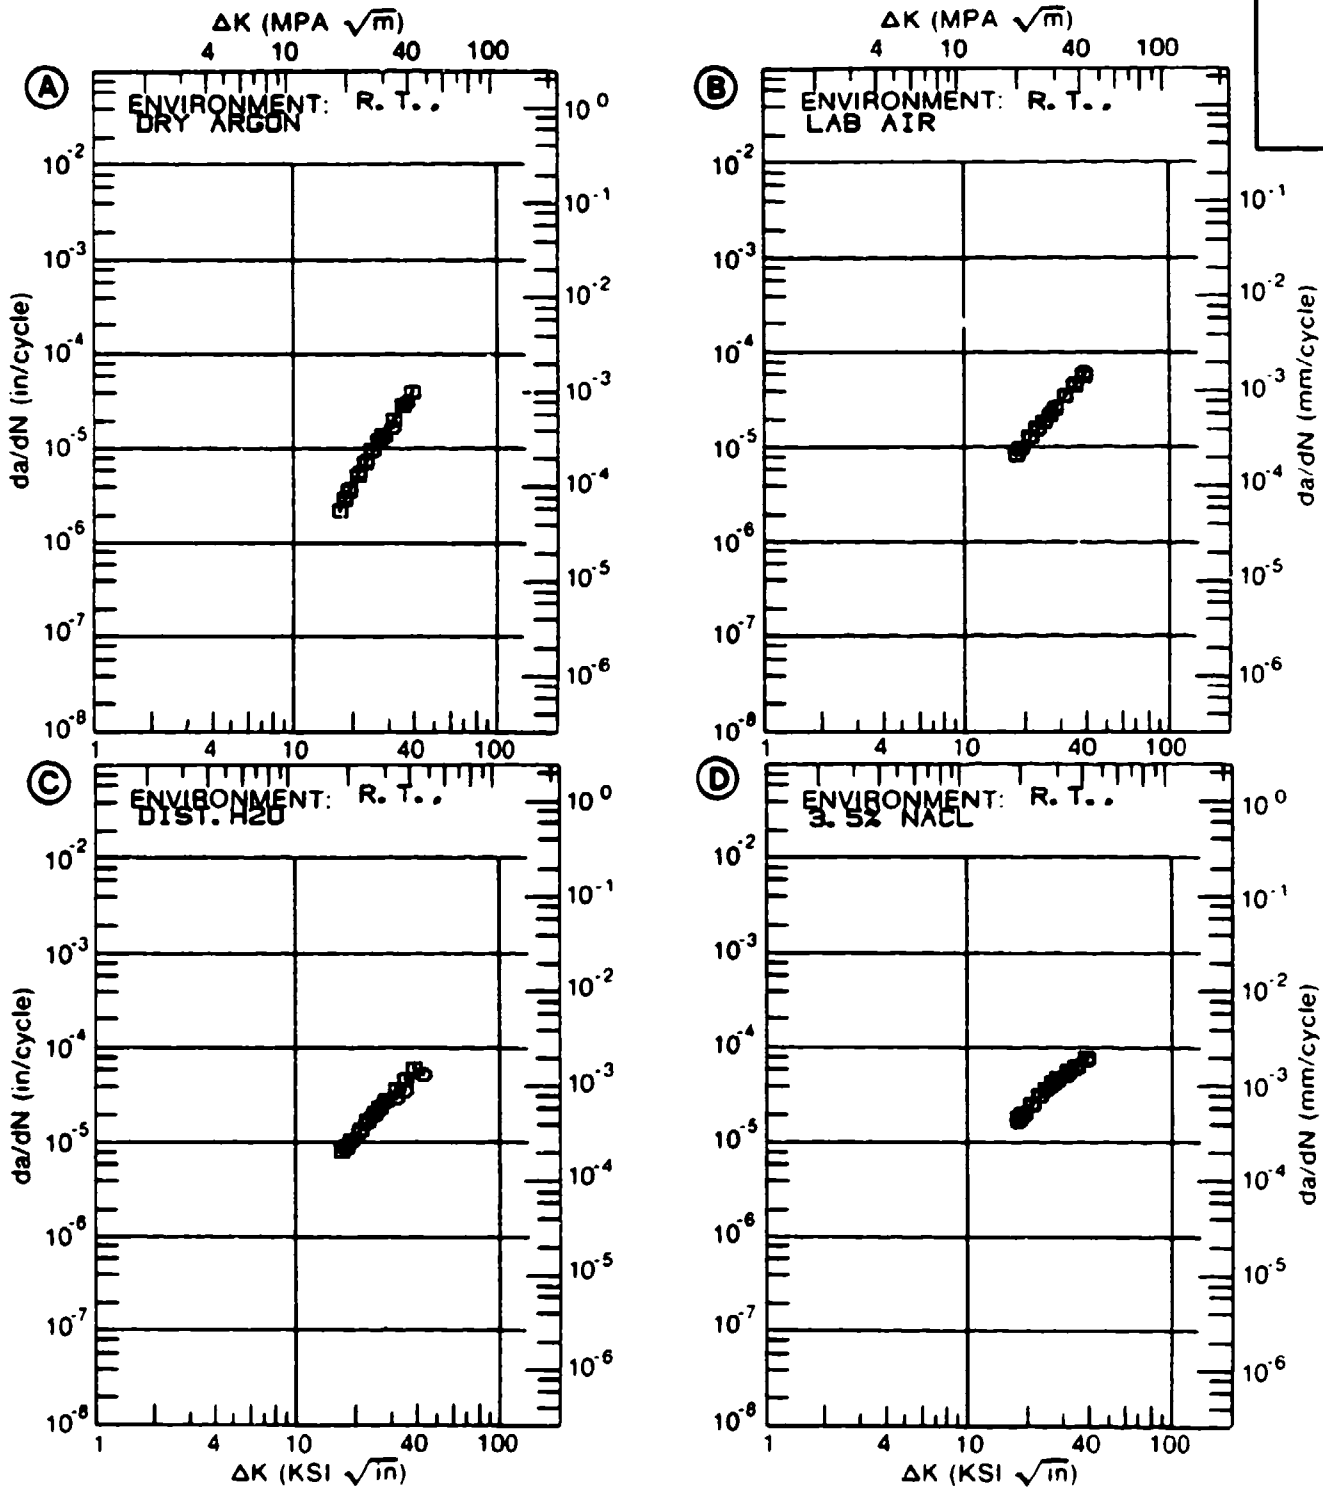


Figure 4.7.3.1

TABLE 4.7.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.7.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-5AL-2.5SN			
CONDITION: ANNEALED					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY ARGON	E= R. T. LAB AIR	E= R. T. DIST. H2O	E= R. T. 3.5% NaCl
DELTA K MIN	A: 18.13	4.02			
	B: 18.23		8.87		
	C: 21.49			16.0	
	D: 20.00				30.2
	20.00	5.56	11.6		
	25.00	11.6	21.3	23.4	51.1
	30.00	20.8	34.4	35.8	69.4
	35.00	33.6	51.0	51.0	86.5
	40.00	50.3	71.3	69.9	105.
	50.00	94.7	124.	124.	157.
DELTA K MAX	A: 53.17	112.			
	B: 53.30		145.		
	C: 53.14			148.	
	D: 53.17				181.
ROOT MEAN SQUARE		4.36	3.18	4.21	4.45
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	2	2	2	2

CONDITION/HT: ANNEALED
 FORM: 0.008" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 30.00 HZ

YIELD STRENGTH: 122.3 KSI
 ULT. STRENGTH: 133.9 KSI
 SPECIMEN THK: 0.003- 0.004"
 SPECIMEN WIDTH: 2.754- 2.764"
 REFERENCES: 00011

TITAN.
 ALLOY

TI-5AL-
 2.5SN

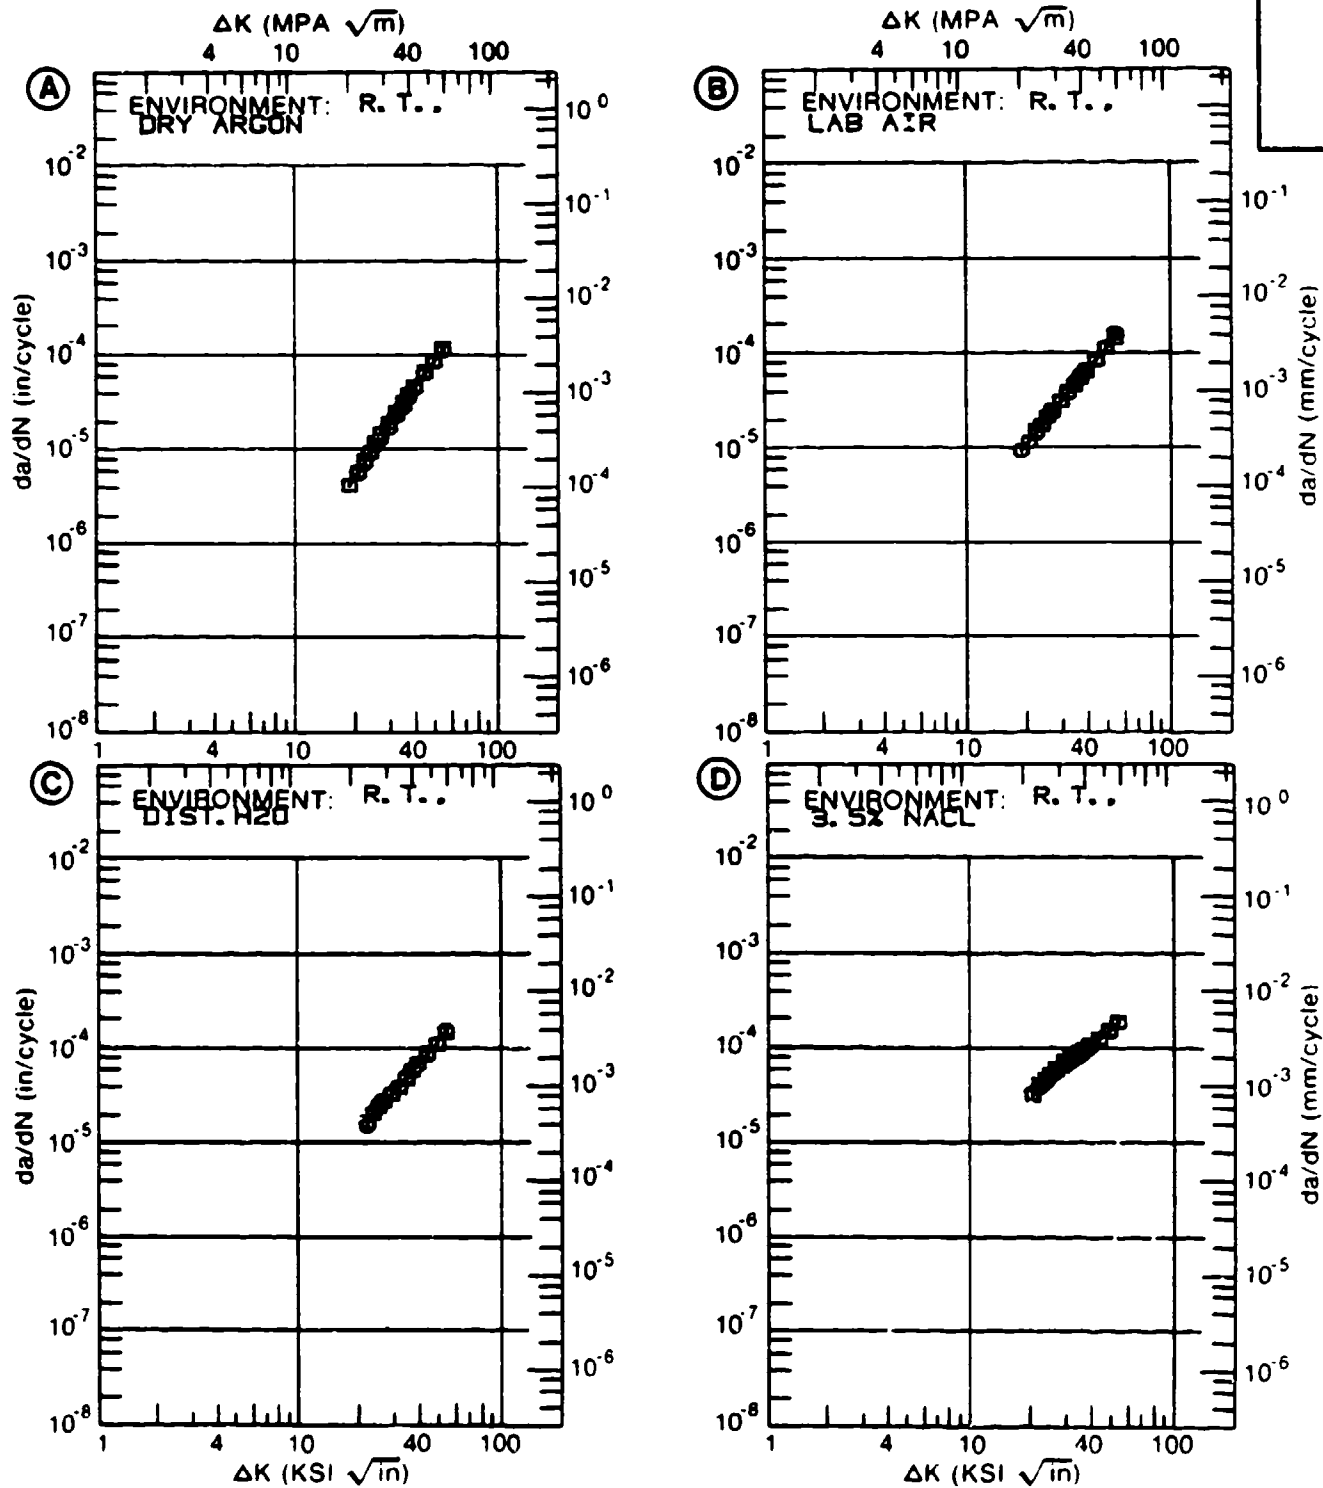


Figure 4.7.3.2

TABLE 4.7.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.7.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-5AL-2.5SN			
CONDITION: ANNEALED					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY ARGON	E= R. T. LAB AIR	E= R. T. DIST. H2O	E= R. T. 3.5% NACL
DELTA K	A: 4.31	.0150			
MIN	B: 3.99		.0597		
	C: 3.44			.0749	
	D: 3.77				.125
	3.50			.0781	
	4.00		.0604	.114	.149
	5.00	.0301	.152	.253	.295
	6.00	.0444	.310	.526	.719
	7.00	.0558	.558	.984	2.34
	8.00	.0782	.922	1.65	5.30
	9.00	.136	1.43	2.51	7.20
	10.00	.278	2.13	3.49	7.97
DELTA K	A: 11.87	.999			
MAX	B: 12.86		5.60		
	C: 12.87			5.99	
	D: 12.93				12.4
ROOT MEAN SQUARE		18.92	14.40	8.05	13.28
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25	3	4	4	4
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: ANNEALED
 FORM: 0.08" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.07
 FREQUENCY: 55.00- 50.30 HZ

YIELD STRENGTH: 122.3 KSI
 ULT. STRENGTH: 133.9 KSI
 SPECIMEN THK: 0.003- 0.005"
 SPECIMEN WIDTH: 2.752- 2.756"
 REFERENCES: 00011

TITAN.
 ALLOY
 TI-5AL-
 2.5SN

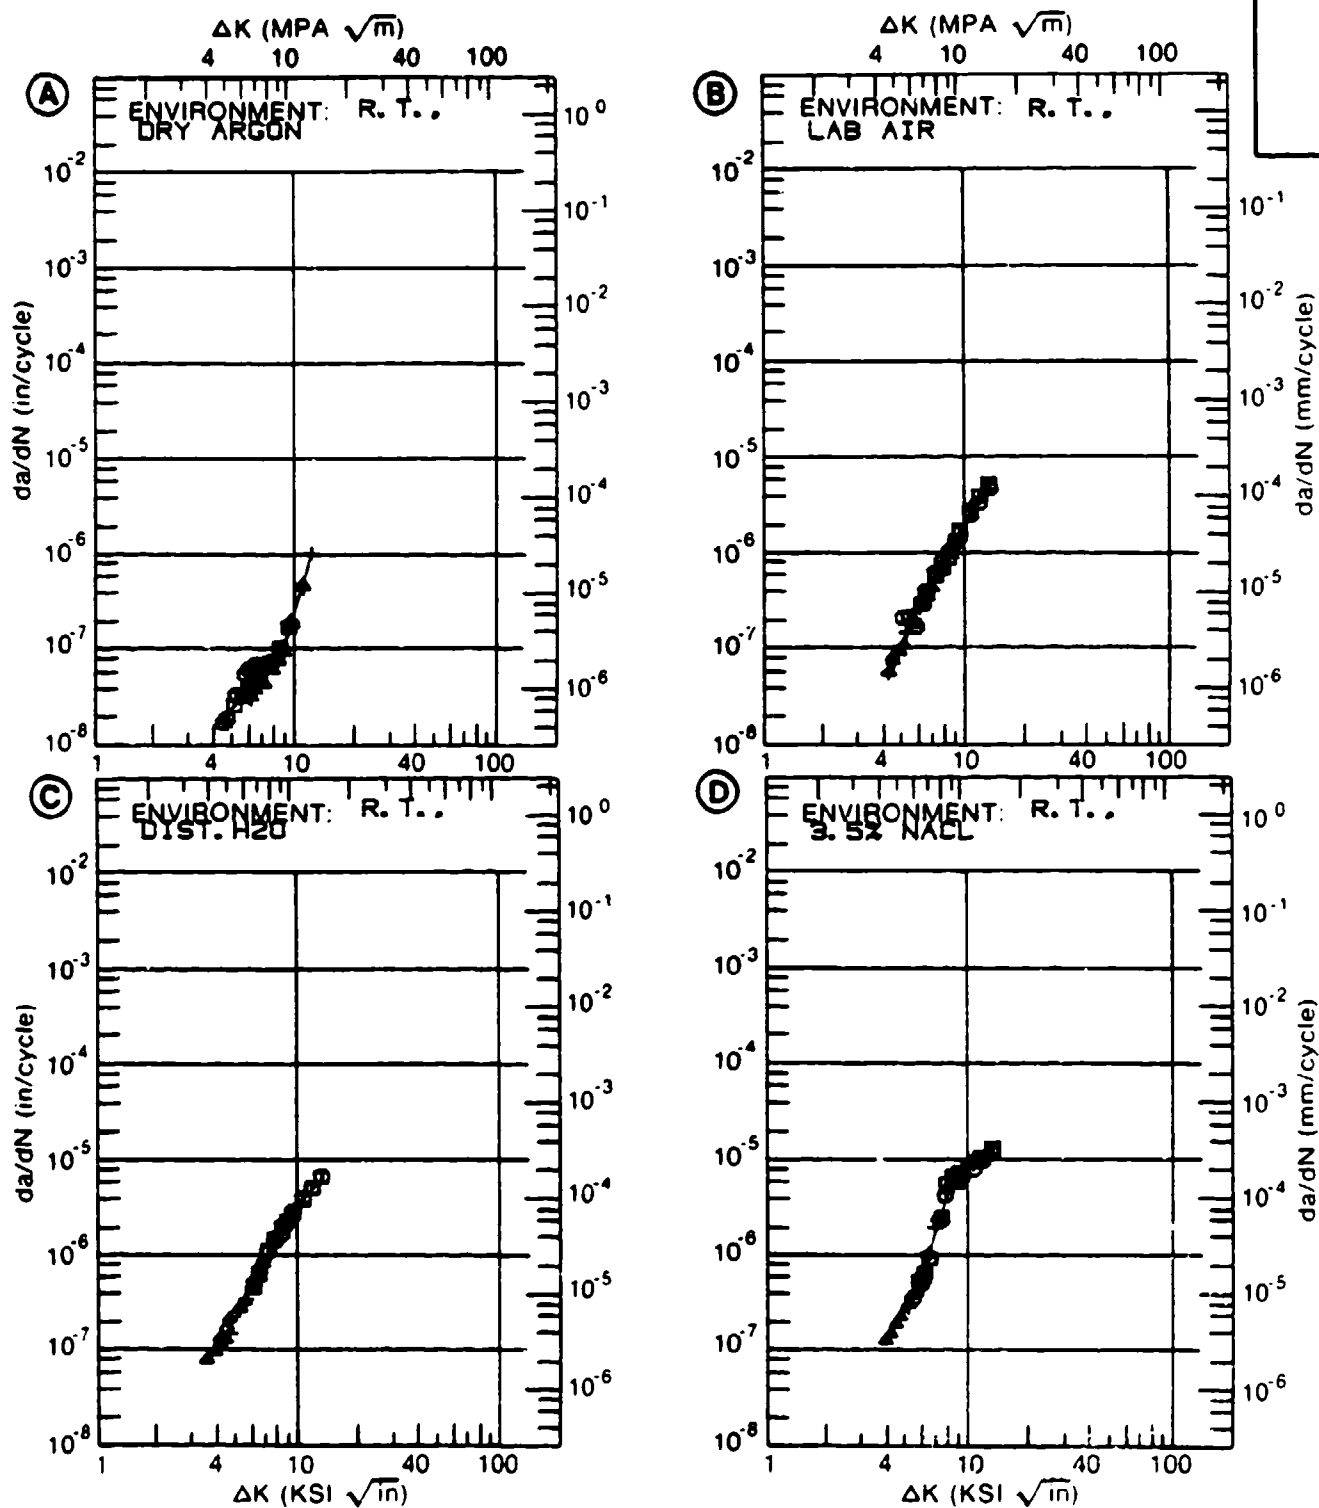


Figure 4.7.3.3

TABLE 4.7.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.7.3.4 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-5AL-2.58N			
CONDITION: ANNEALED					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. DRY ARGON	E= R. T. LAB AIR	E= R. T. DIST. H2O	E= R. T. 3.5% NaCl
DELTA K	A: 17.46	3.21			
MIN	B: 16.63		7.03		
	C: 16.57			7.01	
	D: 16.28				13.7
	20.00	5.35	11.8	12.0	24.5
	25.00	11.7	20.2	21.3	39.2
	30.00	21.2	31.1	33.4	53.7
	35.00	34.7	46.5	49.2	69.3
DELTA K	A: 37.87	44.6			
MAX	B: 38.10		59.5		
	C: 37.79			59.9	
	D: 37.84				79.1
ROOT MEAN SQUARE PERCENT ERROR		3.75	4.85	5.63	5.62
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	2	2	2	2

CONDITION/HT: ANNEALED
 FORM: 0.08" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 50.00- 53.30 HZ

YIELD STRENGTH: 125.4 KSI
 ULT. STRENGTH: 133.9- 135.2 KSI
 SPECIMEN THK: 0.083- 0.085"
 SPECIMEN WIDTH: 2.755- 2.758"
 REFERENCES: 00011

TITAN.
 ALLOY

TI-5AL-
 2.55N

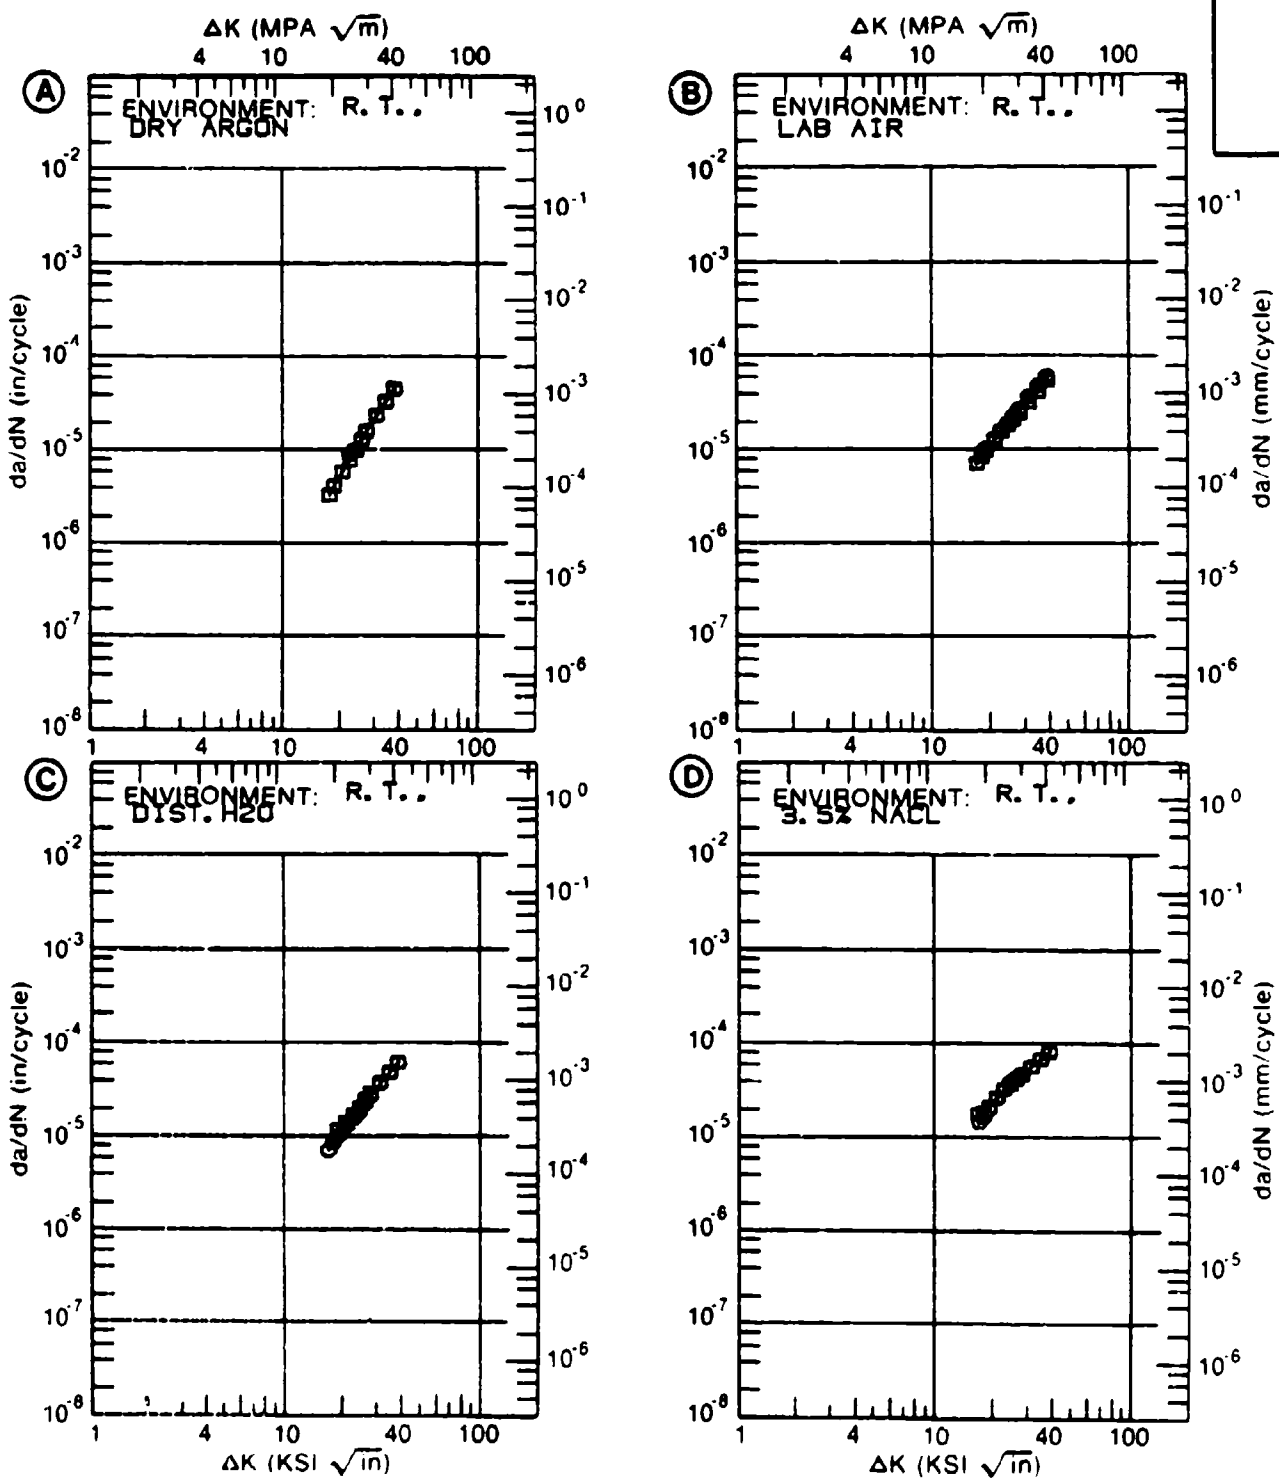


Figure 4.7.3.4

TABLE 4.7.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.7.3.5 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM		TI-5AL-2.5SN			
CONDITION: ANNEALED					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. DRY ARGON	E= R. T. LAB AIR	E= R. T. DIST. H2O	E= R. T. 3.5% NaCl
DELTA K A:	18.62	3.96			
DELTA K B:	19.82		11.5		
MIN C:	18.18			9.45	
D:	21.52				35.6
	20.00	5.38	11.9	12.5	
	25.00	12.4	23.1	23.6	49.4
	30.00	22.2	37.4	38.6	68.1
	35.00	35.5	55.1	57.2	87.1
	40.00	53.5	77.2	79.0	109.
	50.00	114.	141.	130.	176.
DELTA K A:	53.29	145.			
MAX B:	53.22		169.		
C:	53.08			148.	
D:	53.13				207
ROOT MEAN SQUARE		9.40	4.52	5.31	16.48
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	2	2	2	2

CONDITION/HT: ANNEALED
 FORM: 0.00" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 30.00 HZ

YIELD STRENGTH: 125.4 KSI
 ULT. STRENGTH: 193.9- 135.2 KSI
 SPECIMEN THK: 0.003- 0.005"
 SPECIMEN WIDTH: 2.753- 2.757"
 REFERENCES: 00011

TITAN.
 ALLOY

TI-SAL-
 2.5SN

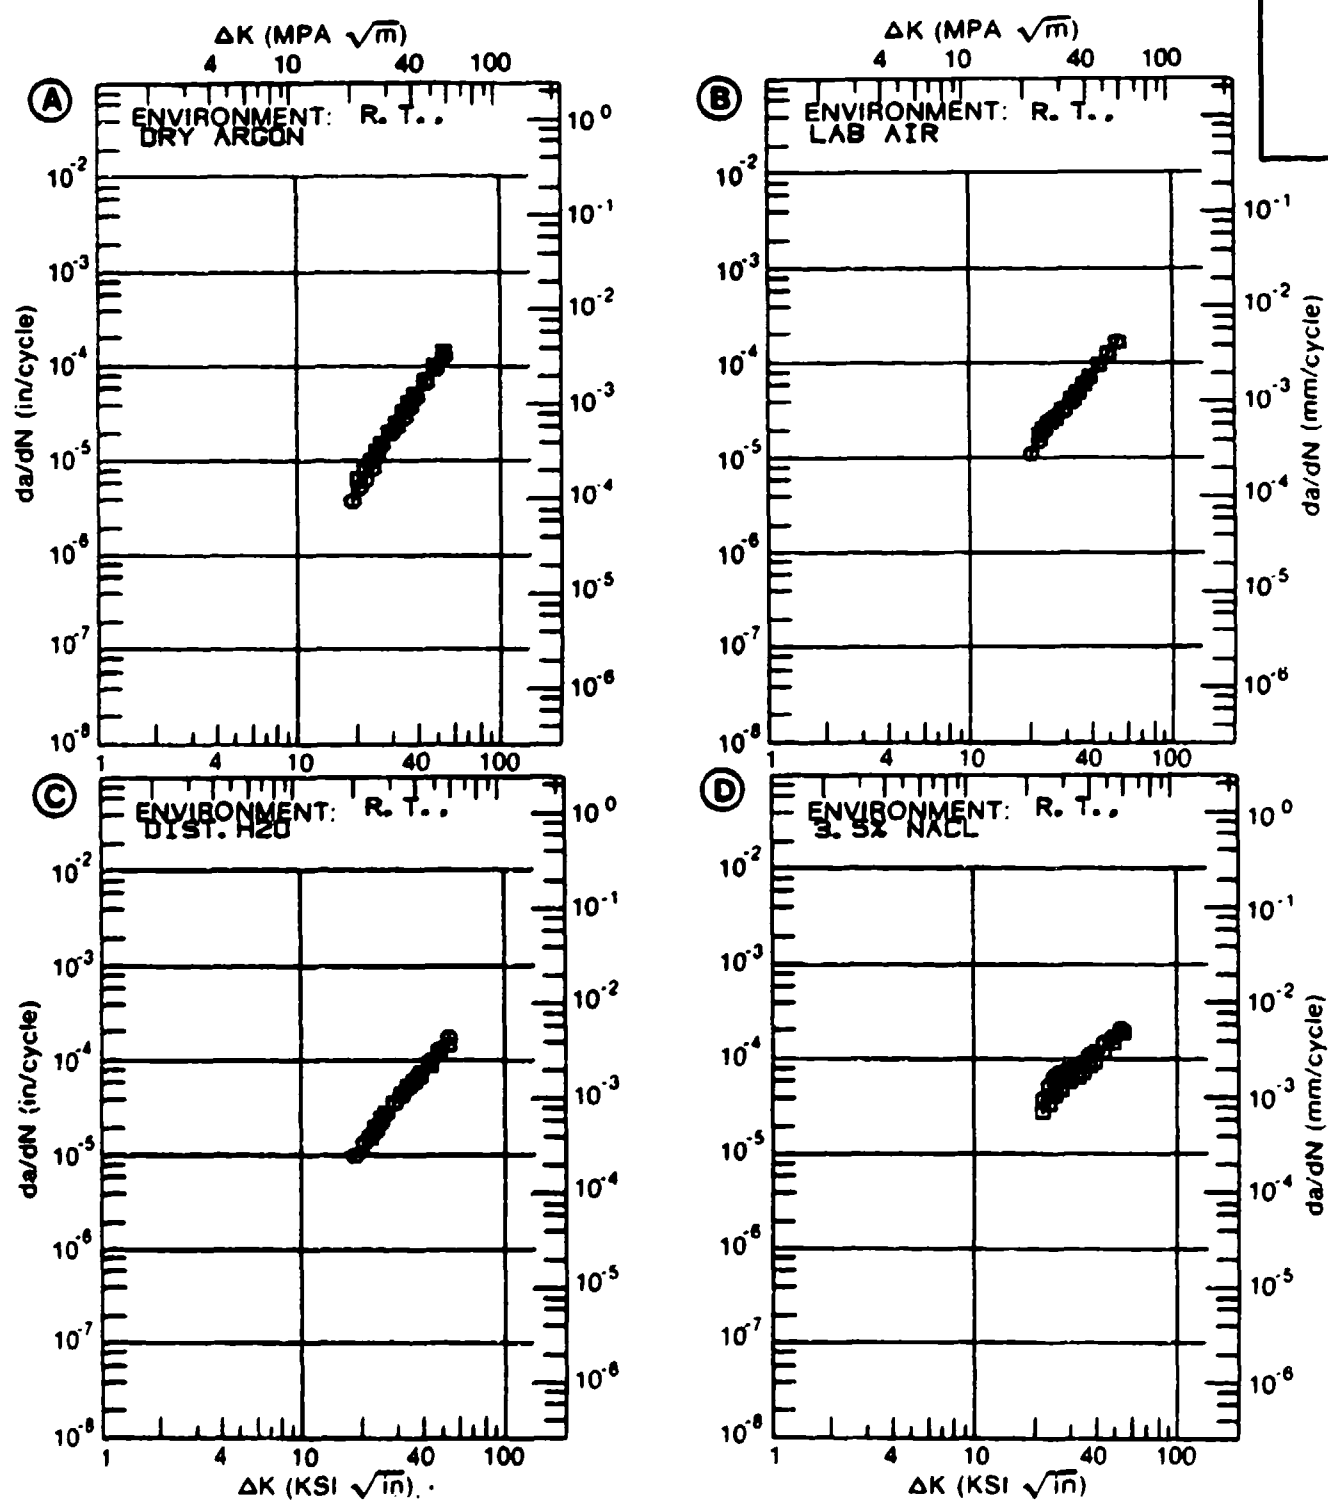


Figure 4.7.3.5

TABLE 4.7.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.7.3.6 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-5AL-2.5SN			
CONDITION: ANNEALED					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. DRY ARGON	E= R. T. LAB AIR	E= R. T. DIST. H2O	E= R. T. 3.5% NaCl
DELTA K A:	5.83	.0930			
DELTA K B:	3.69		.0501		
MIN C:	4.28			.237	
D:	4.23				.209
	4.00		.0662		
	5.00		.158	.363	.981
	6.00	.0905	.347	.658	3.37
	7.00	.105	.685	1.13	6.92
	8.00	.164	1.23	1.81	10.5
	9.00	.285	2.02	2.68	13.1
	10.00	.497	3.08	3.72	14.6
	13.00	1.86	7.57		
DELTA K A:	13.02	1.87			
DELTA K B:	13.07		7.68		
MAX C:	12.74			6.71	
D:	10.00				14.6
ROOT MEAN SQUARE		16.96	11.13	7.18	37.84
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			3
RATIO	0.8-1.25	3	4	4	1
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: ANNEALED
 FORM: 0.08" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.87
 FREQUENCY: 54.20- 58.30 HZ

YIELD STRENGTH: 125.4 KSI
 ULT. STRENGTH: 133.9- 135.2 KSI
 SPECIMEN THK: 0.083- 0.085"
 SPECIMEN WIDTH: 2.753- 2.757"
 REFERENCES: 88911

TITAN.
 ALLOY

TI-5AL-
 2.5SN

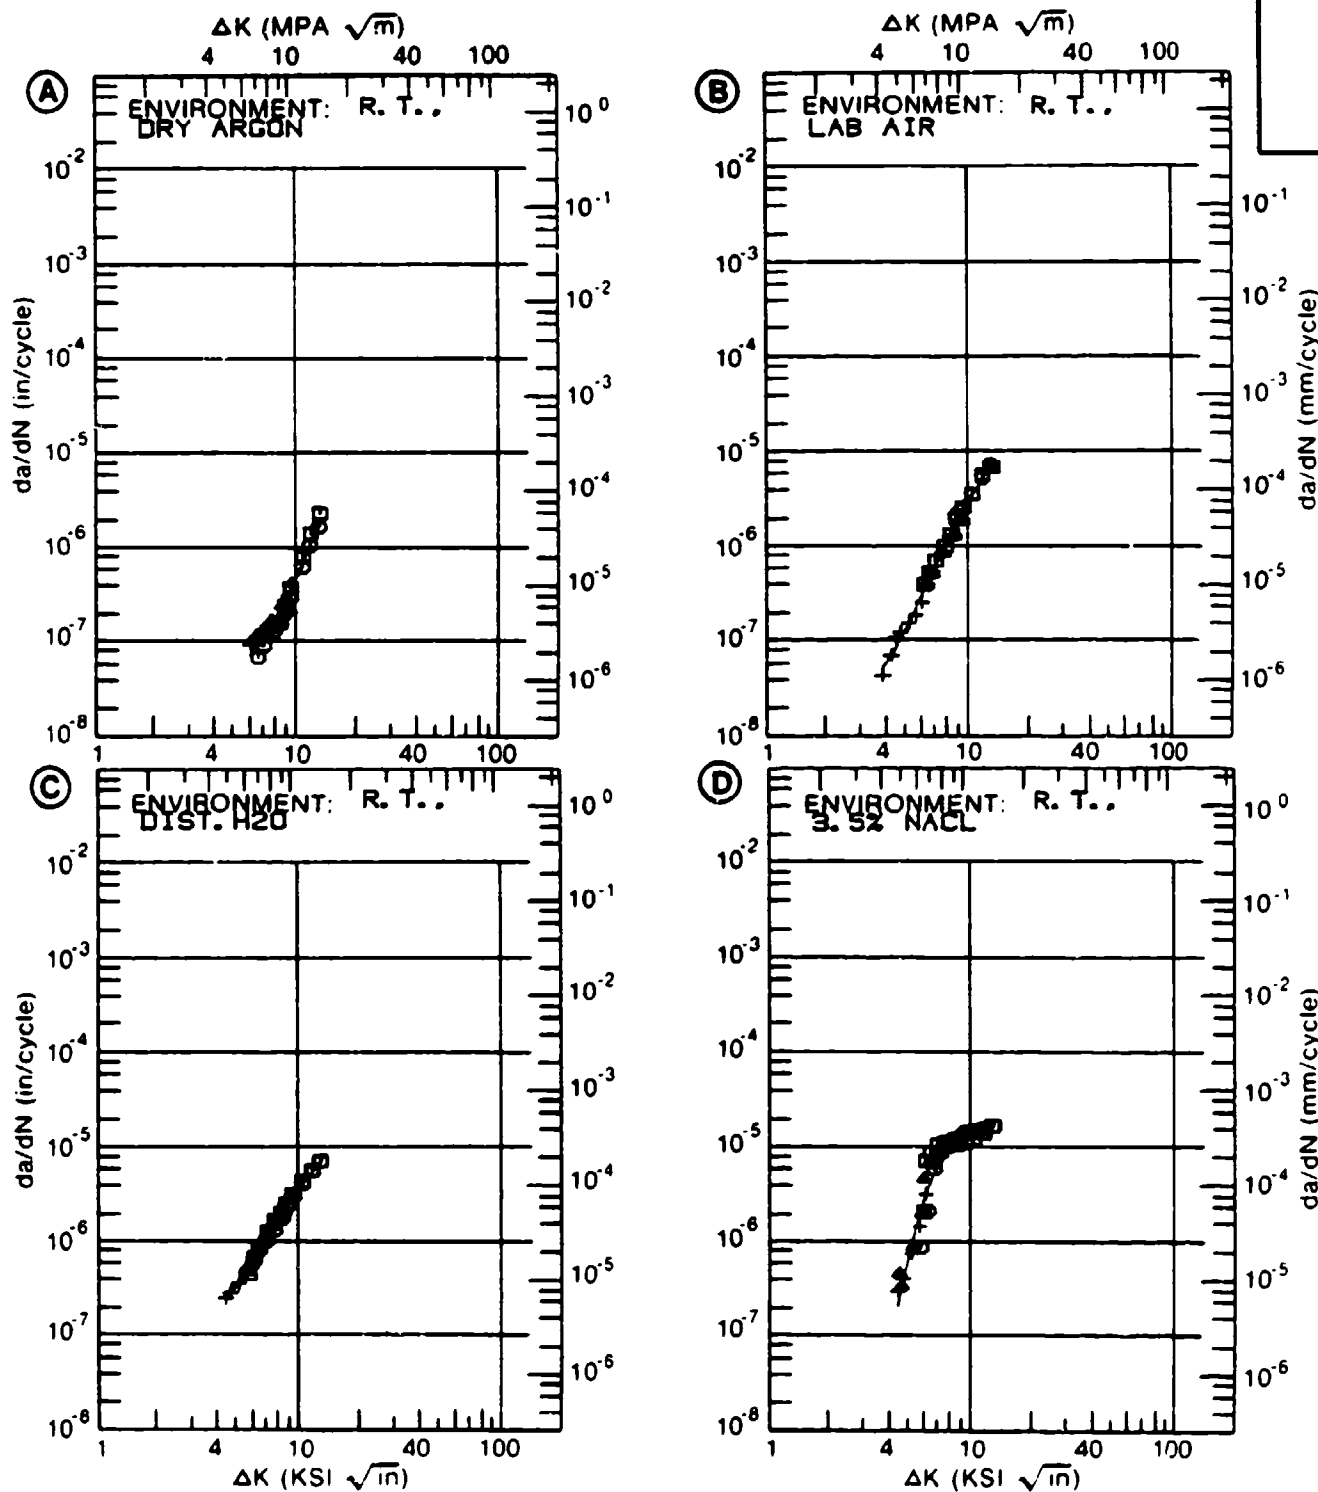


Figure 4.7.3.6

TABLE 4.8.1.1
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM Ti6-2-2-2

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: H.H.A
 AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100
ST	PLATE	0.10	1.00				2.38	13.3	271	
SF	PLATE	0.10	20.00				1.50	10.7	98.4	
STA	PLATE	0.10	1.00				0.16	1.67	17.3	423
STA	PLATE	0.10	20.00				2.37	13.5		

TABLE 4.8.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
TITANIUM Ti6-2-2-2

TEST CONDITIONS

SPECIMEN ORIENTATION -T

ENVIRONMENT: 3.5% NaCl
A T R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
ST	PLATE	0.10	1.00				2.10	47.6	361	
ST	PLATE	0.10	20.00			0.31	4.70	30.7		
STA	PLATE	0.10	1.00						77.4	
STA	PLATE	0.10	20.00			0.47	5.90	15.2		

TABLE 4.8.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.8.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI62222			
CONDITION: ST					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. H. H. A. 1HZ	E= R. T. H. H. A. 20HZ	E= R. T. 3. 5% NACL 1HZ	E= R. T. 3. 5% NACL 20HZ
DELTA K	A: 8.23 :	1.20			
MIN	B: 5.05 :		.076		
	C: 6.77 :			.584	
	D: 3.89 :				.048
	4.00 :				.0691
	5.00 :				.319
	6.00 :		.186		.742
	7.00 :		.378	.630	1.39
	8.00 :		.659	.915	2.27
	9.00 :	1.67	1.03	1.38	3.37
	10.00 :	2.38	1.50	2.10	4.70
	13.00 :	4.98	3.45	6.80	10.0
	16.00 :	8.12	6.12	18.0	17.6
	20.00 :	13.3	10.7	47.6	30.7
	25.00 :	22.3	18.2	110.	50.9
	30.00 :	36.4	27.7	194.	73.5
	35.00 :	59.0	39.8	291.	96.6
	40.00 :	96.4	55.1	390.	119.
	50.00 :	271.	98.4	561.	
	60.00 :	834.		673.	
	70.00 :	2775.			
DELTA K	A: 71.40 :	3301.			
MAX	B: 56.48 :		139.		
	C: 63.48 :			697.	
	D: 49.43 :				155.
ROOT MEAN SQUARE		8.80	8.83	22.49	11.12
PERCENT ERROR					
LIFE	0.0-0.5				1
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1	1	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: ST
 FORM: 0.83" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY:

YIELD STRENGTH: 157.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.151- 0.152"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: 86844

TITAN.
 ALLOY

TI-6-2-
 2-2-2

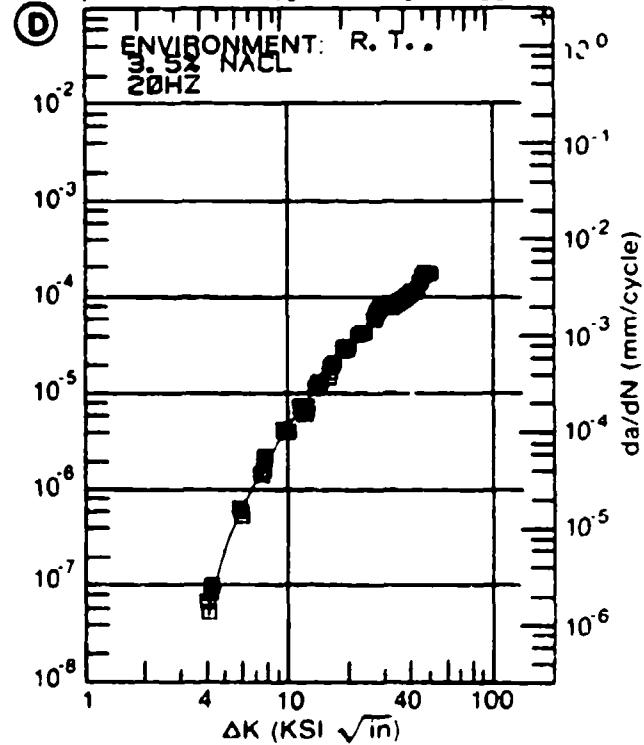
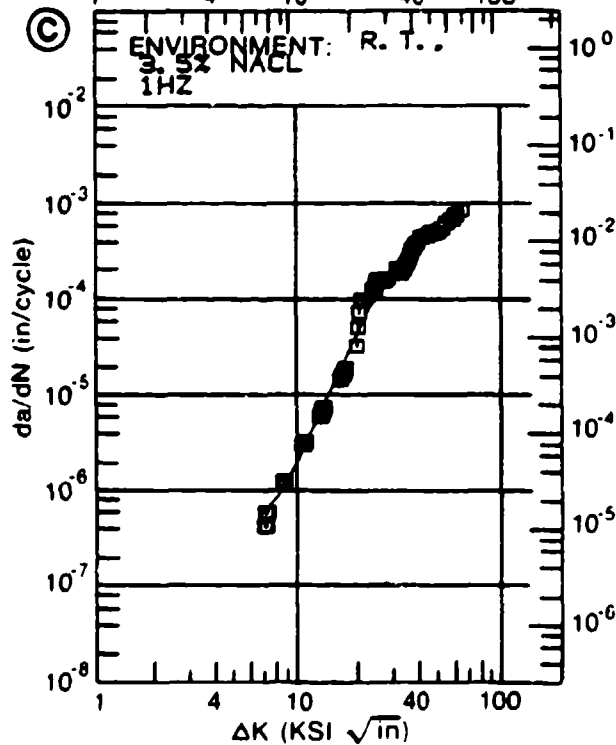
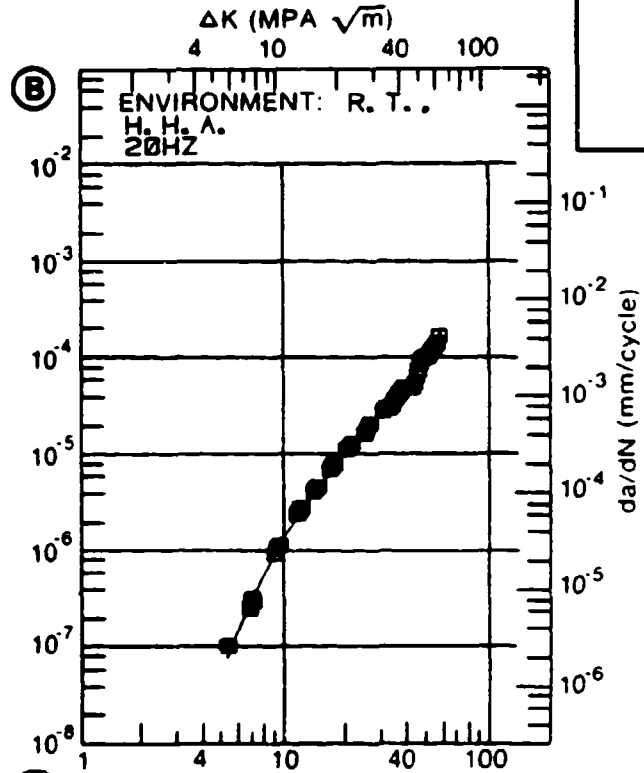
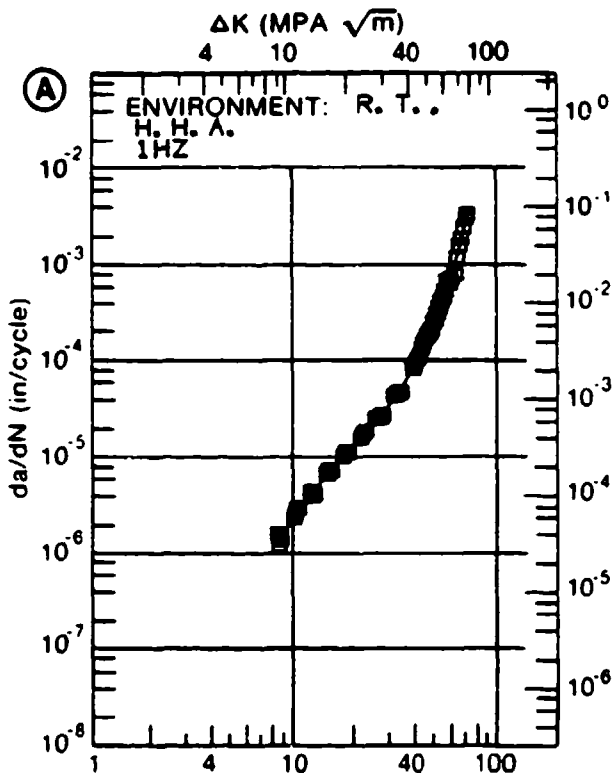


Figure 4.8.3.1

TABLE 4.8.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.8.3.2 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM

TI62222

CONDITION: STA

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. H. H. A. 1HZ	E= R. T. H. H. A. 20HZ	E= R. T. 3. 5% NACL 1HZ	E= R. T. 3. 5% NACL 20HZ
DELTA K	A: 7.18	.54			
MIN	B: 4.13		.06		
	C: 16.00			35.9	
	D: 3.64				.06
	4.00				.125
	5.00		.164		.471
	6.00		.369		1.13
	7.00		.686		3.09
	8.00	.811	1.12		3.27
	9.00	1.26	1.69		4.57
	10.00	1.87	2.37		5.90
	13.00	4.73	5.02		9.60
	16.00	9.07	8.36	35.9	12.5
	20.00	17.3	13.5	77.4	15.2
	25.00	32.7	20.3		
	30.00	56.9	27.1		
	35.00	95.6	33.8		
	40.00	158.	40.2		
	50.00	423.			
	60.00	1195.			
DELTA K	A: 64.83	2030.			
MAX	B: 41.87		42.5		
	C: 20.37			78.9	
	D: 20.05				15.2

ROOT MEAN SQUARE 7.39 8.43 14.68 20.21
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1 1 1
SUMMARY 1.25-2.0 1
(NP/NA) >2.0

CONDITION/HT: STA
 FORM: 0.89" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY:

YIELD STRENGTH: 157.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.143- 0.147"
 SPECIMEN WIDTH: 3.070"
 REFERENCES: 88844

TITAN.
 ALLOY

TI-6-2-
 2-2-2

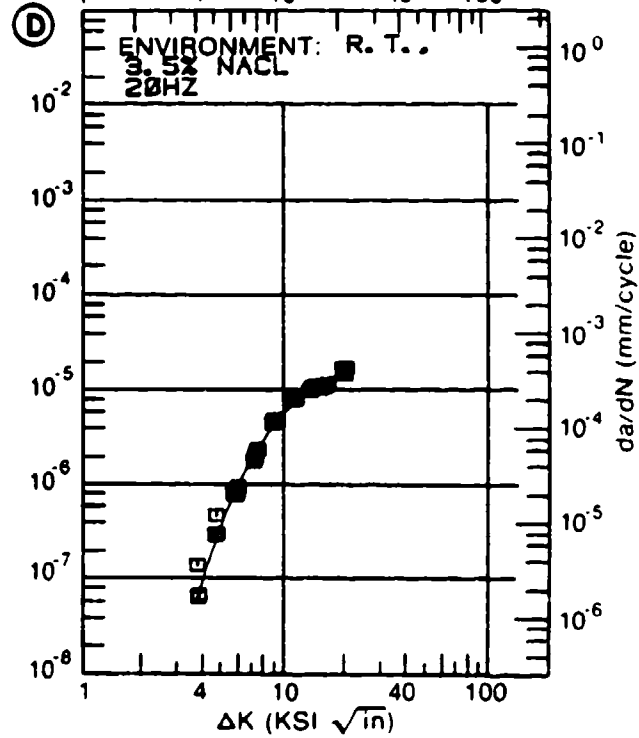
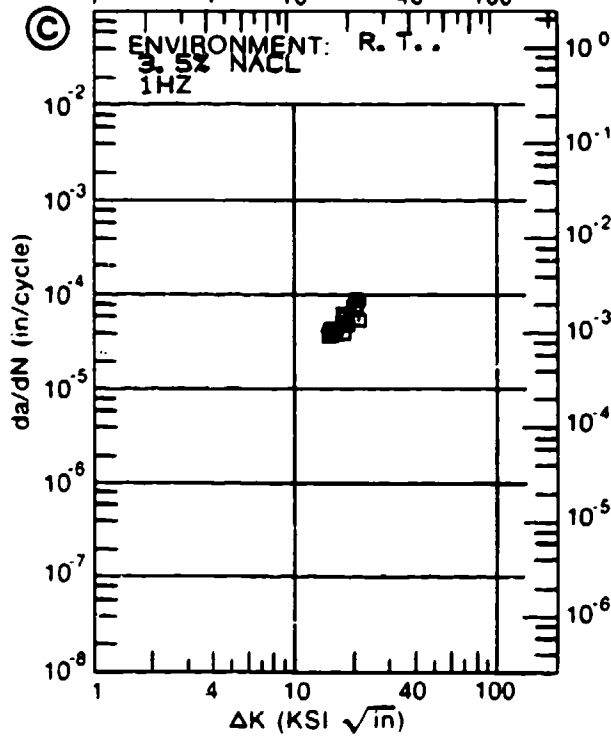
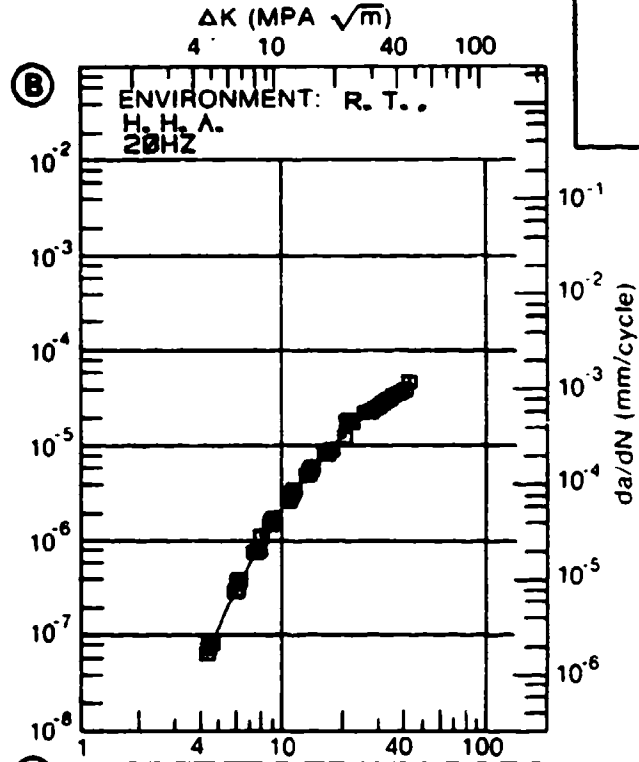
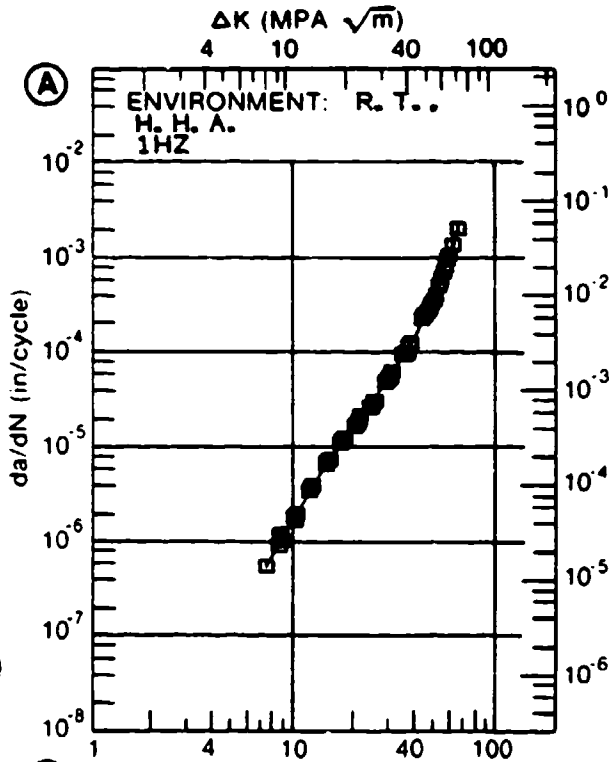


Figure 4.8.3.2

TABLE 4.9.1.1.1

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6-2-4-2

TEST CONDITIONS

SPECIMEN ORIENTATION C-R

ENVIRONMENT: LAB AIR AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 5 10 20 50 100	
1790F 1HR AC. 1100F 8HRS AC	FORGING	0.10	0.16		10.3
1790F 1HR AC. 1100F 8HRS AC	FORGING	0.50	0.16		2.27

TABLE 4.9.1.2

CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM T1-6-2-4-2

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
1790F 1HR AC. 1100F 6HRS AC	FORGING	0.10	30.00	2.5	0.27
1790F 1HR AC. 1100F 6HRS AC	FORGING	0.50	-----	5	5.69
1790F 1HR AC. 1100F 6HRS AC	FORGING	0.70	0.16	10	20.9
				50	5.35
				100	

ENVIRONMENT: AIR AT 800 F

TABLE 4.9.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6-2-4-2

TEST CONDITIONS

SPECIMEN
ORIENTATION C-RENVIRONMENT
AIR AT 1000 F

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	ENVIRONMENT		FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE)						
				DELTA K LEVELS (KSI SQRT(IN))	AIR AT 1000 F	2	5	10	20	50	100	
1790F 1HR AC. 1100F 8HRS AC	FORGING	0.10	30.00					2	24			
1790F 1HR AC. 1100F 8HRS AC	FORGING	0.50	0.16					9	16	30	2	

TABLE 4.9.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.9.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6-2-4-2			
CONDITION: 1790F 1HR AC, 1100F 8HRS AC					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K	A: 11.61	1.81			
MIN	B: 7.05		.52		
	C:				
	D:				
	8.00		.919		
	9.00		1.50		
	10.00		2.27		
	13.00	2.52	5.70		
	16.00	4.82	10.5		
	20.00	10.3			
DELTA K	A: 24.68	22.0			
MAX	B: 19.52		17.1		
	C:				
	D:				
ROOT MEAN SQUARE		7.82	9.78		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: 1700F 1HR AC, 1100F 8HRS AC
 FORM: 2.00" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 FREQUENCY: 0.10 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 139.4 KSI
 ULT. STRENGTH: 151.6 KSI
 SPECIMEN THK: 0.079"
 SPECIMEN WIDTH: 1.750"
 REFERENCES: PW002

TITAN.
 ALLOY

TI-6-2-
 4-2

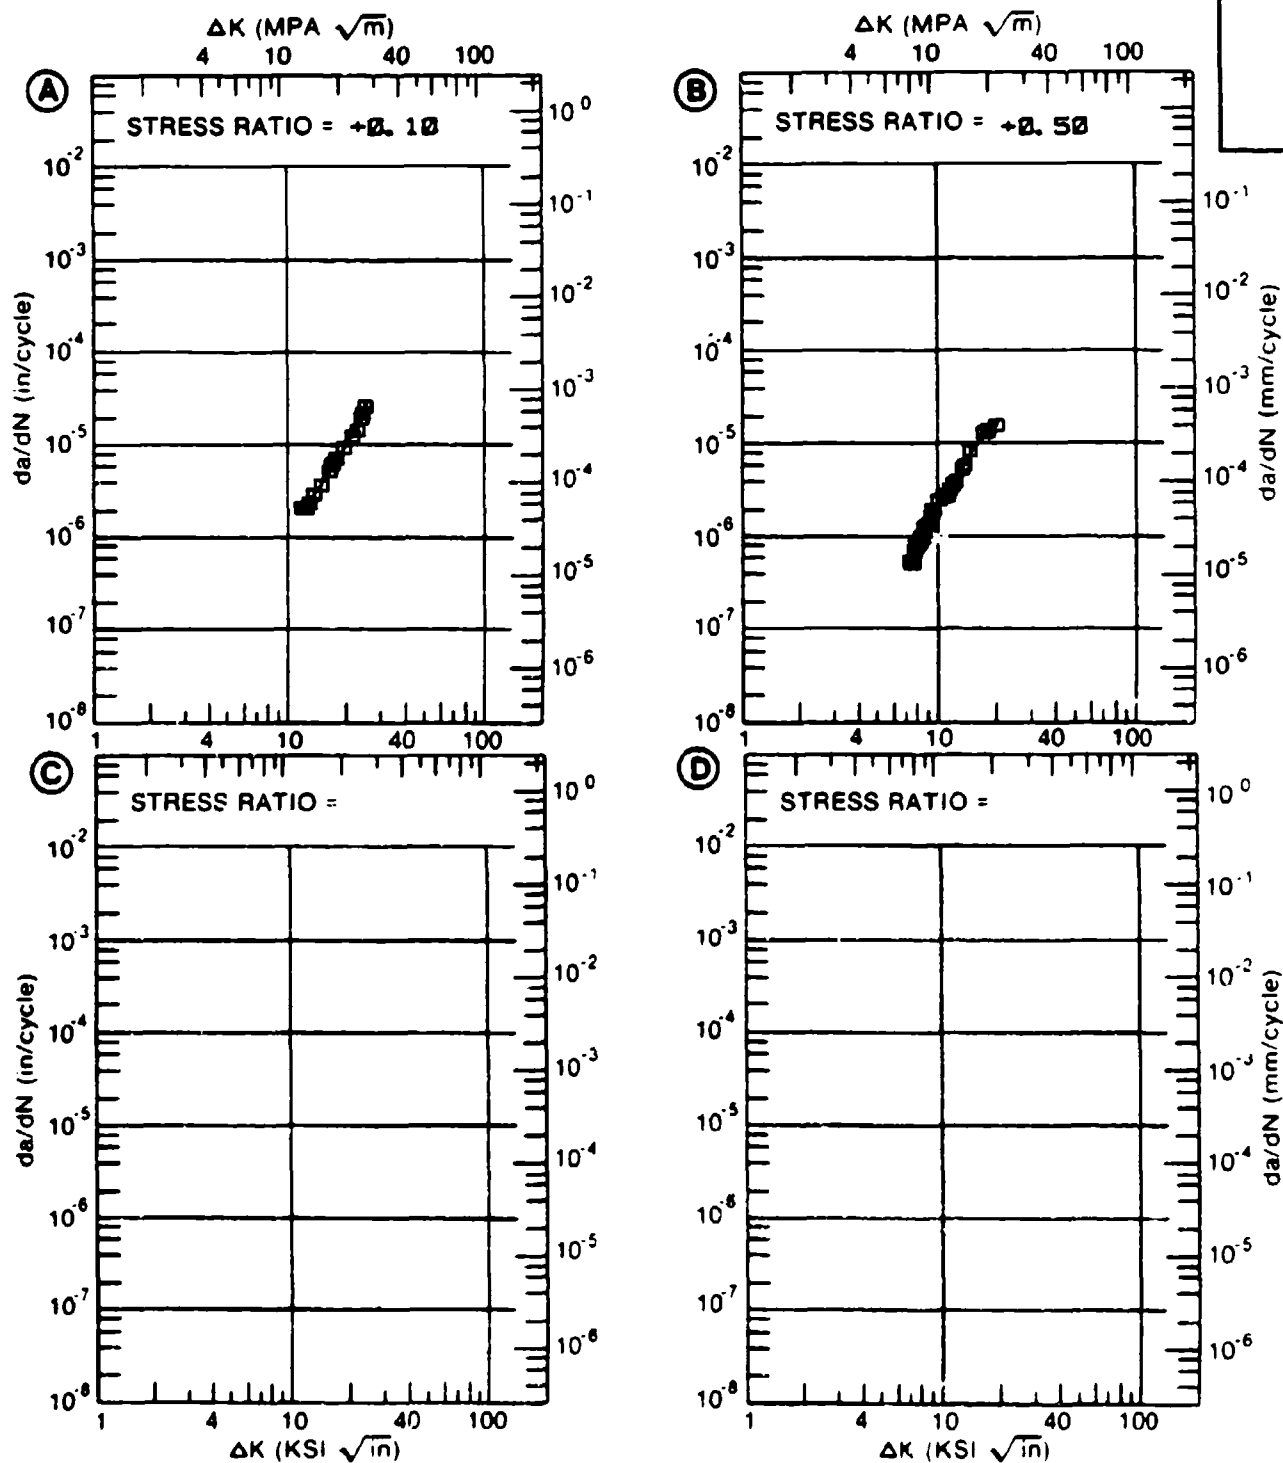


Figure 4.9.3.1

TABLE 4.9.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.9.3.2 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6-2-4-2
CONDITION: 1790F 1HR AC, 1100F 8HRS AC
ENVIRONMENT: + 800F, AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.70			
DELTA K MIN	A: 5.15	1.36			
	B:				
	C:				
	D:				
	6.00	2.04			
	7.00	2.71			
	8.00	3.36			
	9.00	4.16			
	10.00	5.35			
	13.00	15.5			
DELTA K MAX	A: 13.08	16.0			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 15.01
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1780F 1HR AC, 1100F 8HRS AC
 FORM: 2.00" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 FREQUENCY: 0.18 HZ
 ENVIRONMENT: + 800° F, AIR

YIELD STRENGTH: 135.5- 140.9 KSI
 ULT. STRENGTH: 148.5- 152.3 KSI
 SPECIMEN THK: 0.080- 0.081"
 SPECIMEN WIDTH: 1.750"
 REFERENCES: PW002

TITAN.
 ALLOY

TI-6-2-
 4-2

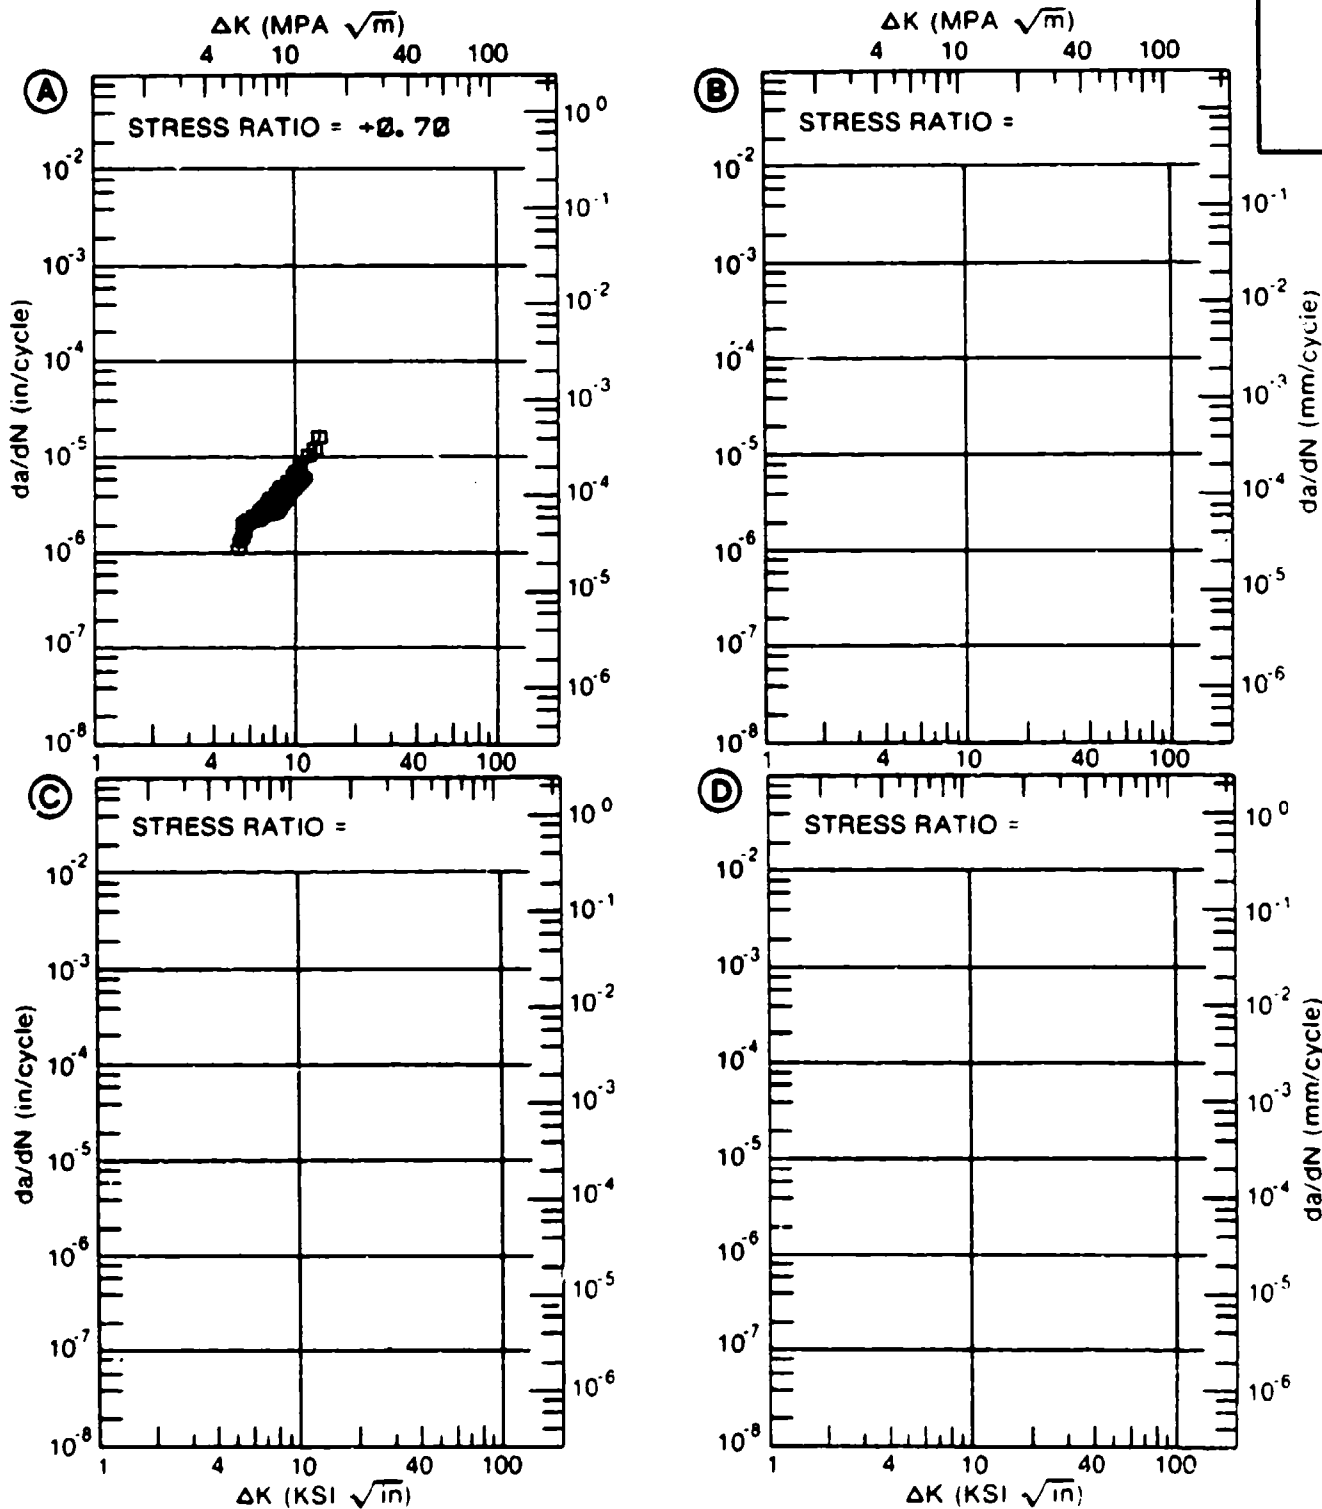


Figure 4.9.3.2

TABLE 4.9.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.9.3.3 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6-2-4-2
CONDITION: 1790F 1HR AC, 1100F 8HRS AC
ENVIRONMENT: +1000F, AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.50			
DELTA K MIN	A: 5.60	3.89			
	B:				
	C:				
	D:				
	6.00	4.28			
	7.00	5.34			
	8.00	6.50			
	9.00	7.77			
	10.00	9.16			
	13.00	14.0			
	16.00	20.1			
	20.00	30.2			
DELTA K MAX	A: 20.12	30.5			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE PERCENT ERROR 4.85

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1700F 1HR AC, 1100F 8HRS AC
 FORM: 2.00" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 FREQUENCY: 0.18 HZ
 ENVIRONMENT: +1000° F, AIR

YIELD STRENGTH: 139.4 KSI
 ULT STRENGTH: 151.8 KSI
 SPECIMEN THK: 0.074"
 SPECIMEN WIDTH: 1.750"
 REFERENCES PW002

TITAN.
 ALLOY

TI-6-2-
 4-2

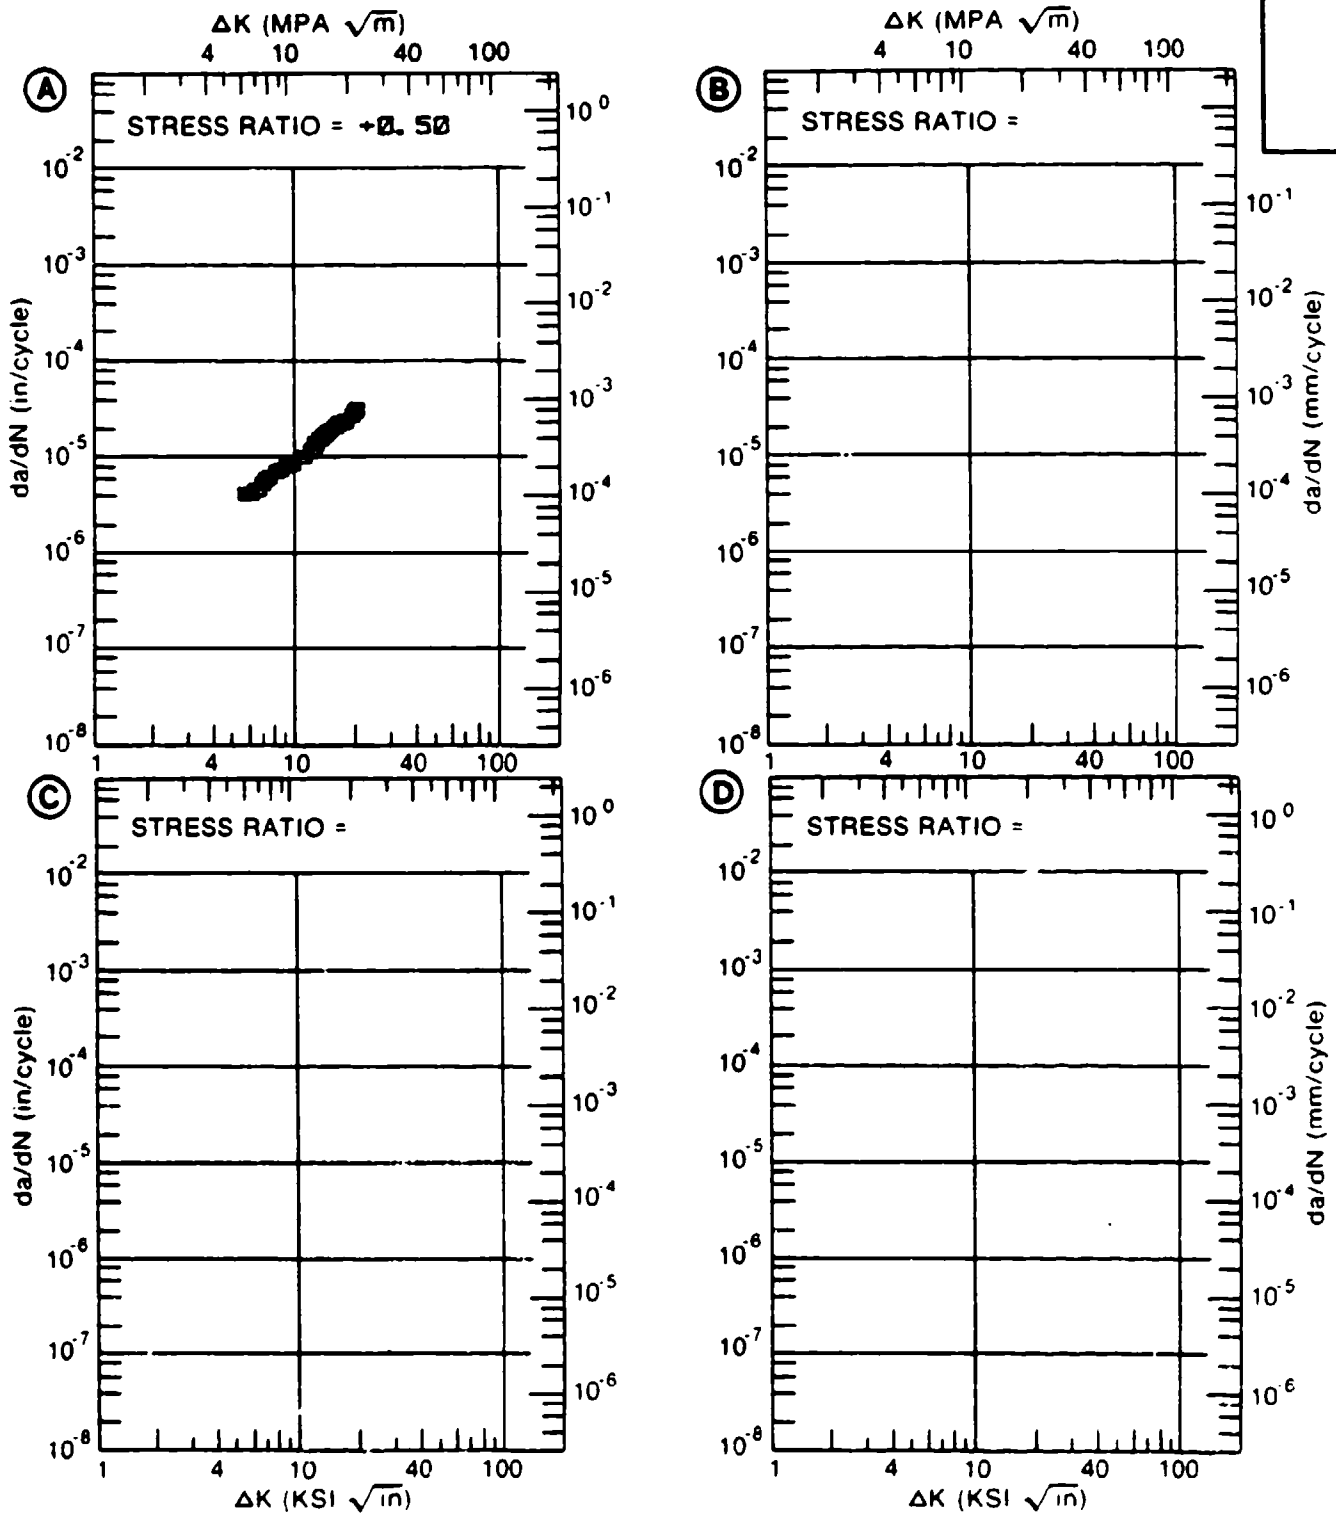


Figure 4.9.3.3

TABLE 4.9.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.9.3.4 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6-2-4-2			
CONDITION: 1750F 1HR AC, 1100F 8HRS AC					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E=+ 800F	E=+1000F		
		AIR	AIR		
DELTA K MIN	A: 4.95	.26			
	B: 5.44		.70		
	C:				
	D:				
	5.00	.270			
	6.00	.378	.846		
	7.00	.511	1.12		
	8.00	.682	1.43		
	9.00	.910	1.80		
	10.00	1.22	2.24		
	13.00	2.99	4.34		
	16.00	6.35	8.64		
DELTA K MAX	A: 18.28	9.39			
	B: 18.45		15.5		
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		5.98	4.40		
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25				
	1.25-2.0				
	>2.0				

CONDITION/HT: 1700F 1HR AC, 1100F 8HRS AC
 FORM: 2.00" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 STRESS RATIO: +0.10
 FREQUENCY: 30.00 HZ

YIELD STRENGTH: 139.4- 140.9 KSI
 ULT. STRENGTH: 151.6- 152.3 KSI
 SPECIMEN THK: 0.073- 0.083"
 SPECIMEN WIDTH: 1.750"
 REFERENCES: PW002

TITAN.
 ALLOY

TI-6-2-
 4-2

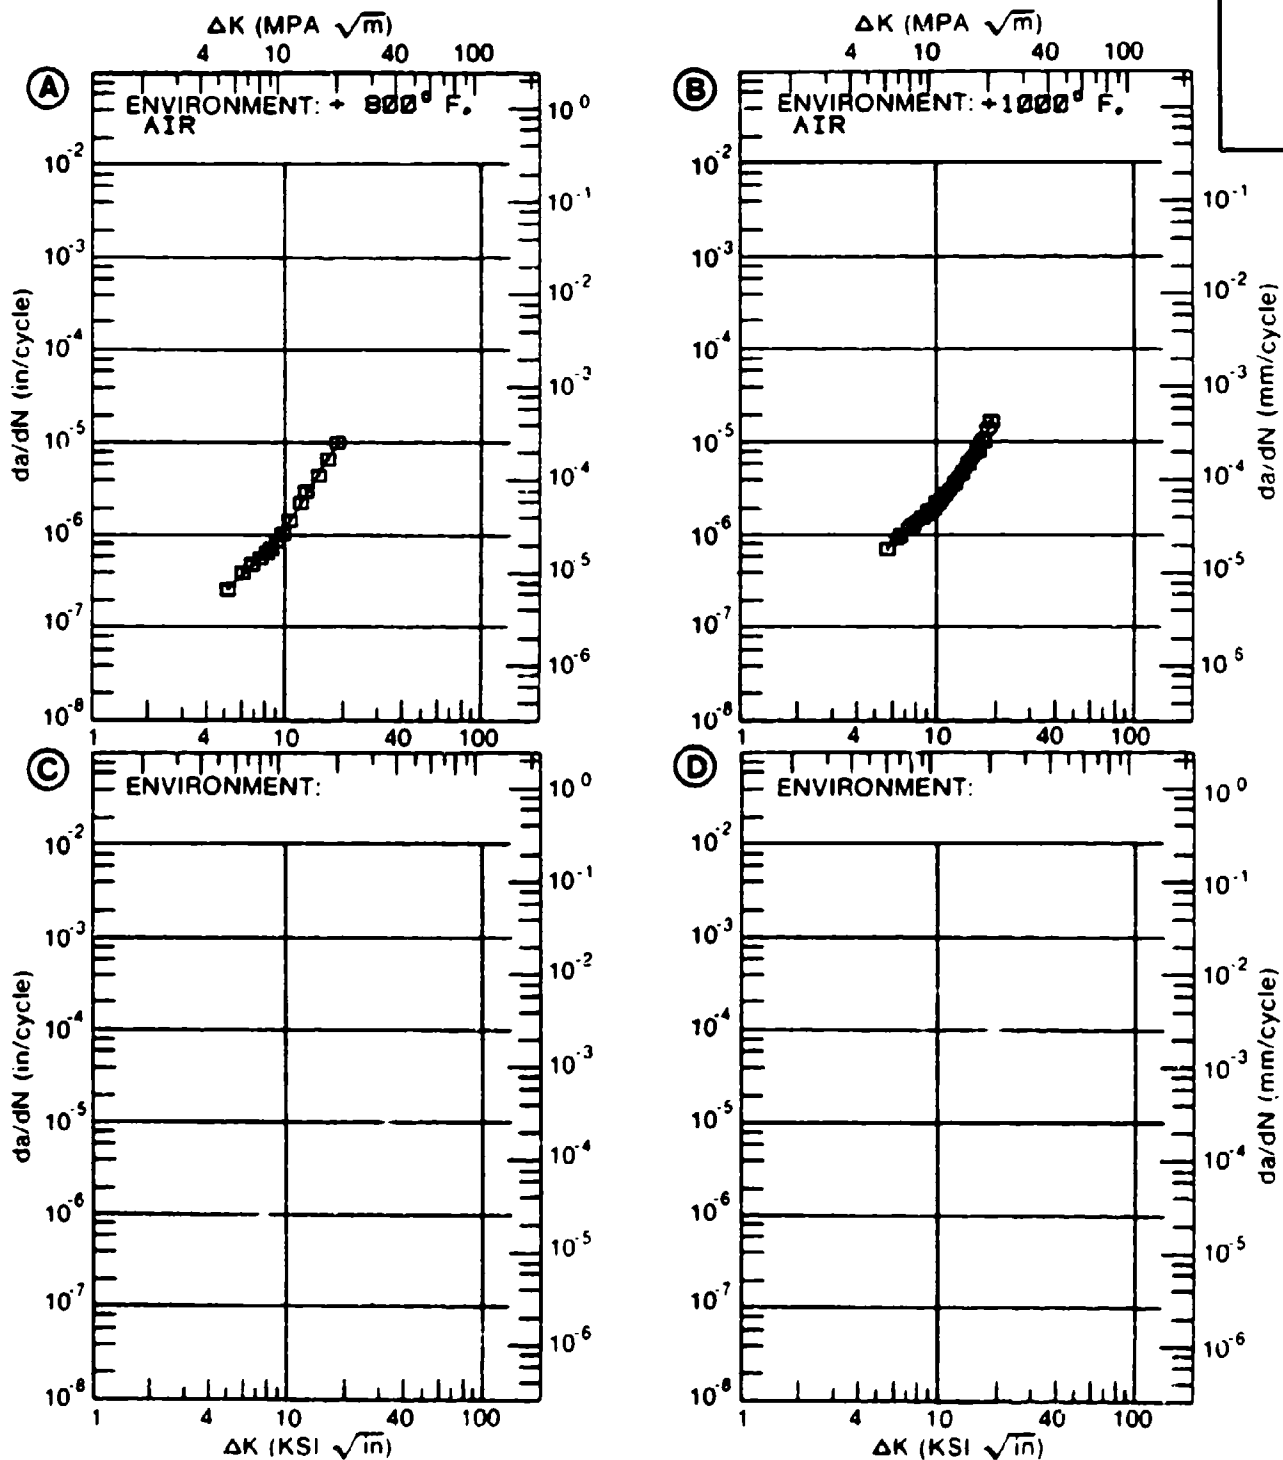


Figure 4.9.3.4

TABLE 4.9.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.9.3.5 INDICATING EFFECT
OF FREQUENCY

MATERIAL: TITANIUM TI-6-2-4-2
CONDITION: 1790F 1HR AC, 1100F 8HRS AC
ENVIRONMENT: + 800F, AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		F(HZ)=2 MIN. HOLD TRAPEZOIDAL WAVEFORM			
DELTA K MIN	A:	8.97	5.44		
	B:				
	C:				
	D:				
		9.00	5.44		
		10.00	5.69		
	13.00	7.89			
	16.00	12.0			
	20.00	20.9			
DELTA K MAX	A:	22.81	29.5		
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		7.30			
PERCENT ERROR					

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1700F 1HR AC, 1100F 8HRS AC
 FORM: 2.00" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 STRESS RATIO: +0.50
 ENVIRONMENT: + 800° F, AIR

YIELD STRENGTH: 140.9 KSI
 ULT. STRENGTH: 152.3 KSI
 SPECIMEN THK: 0.082"
 SPECIMEN WIDTH: 1.750"
 REFERENCES: PW002

TITAN.
 ALLOY
 TI-6-2-
 4-2

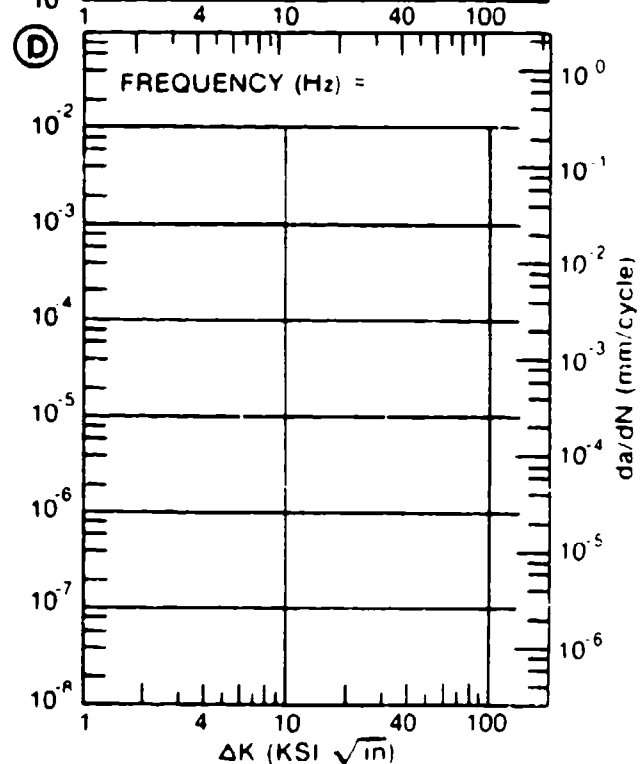
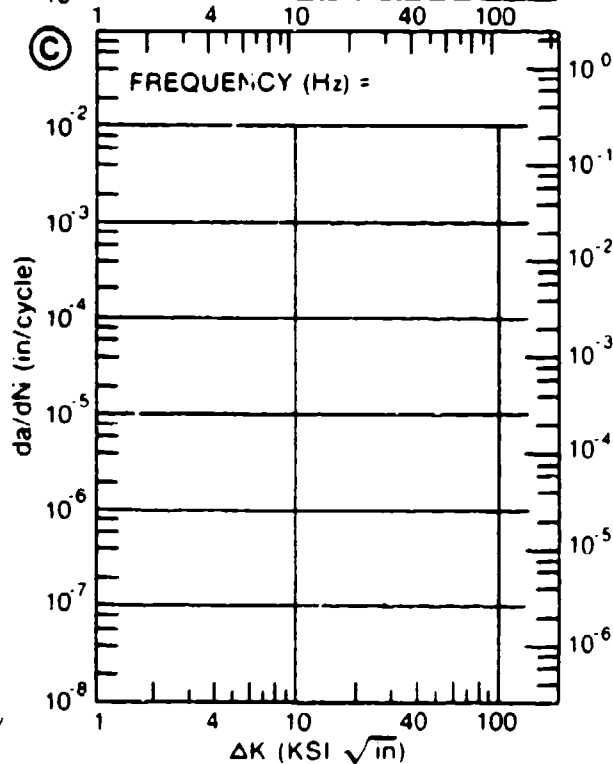
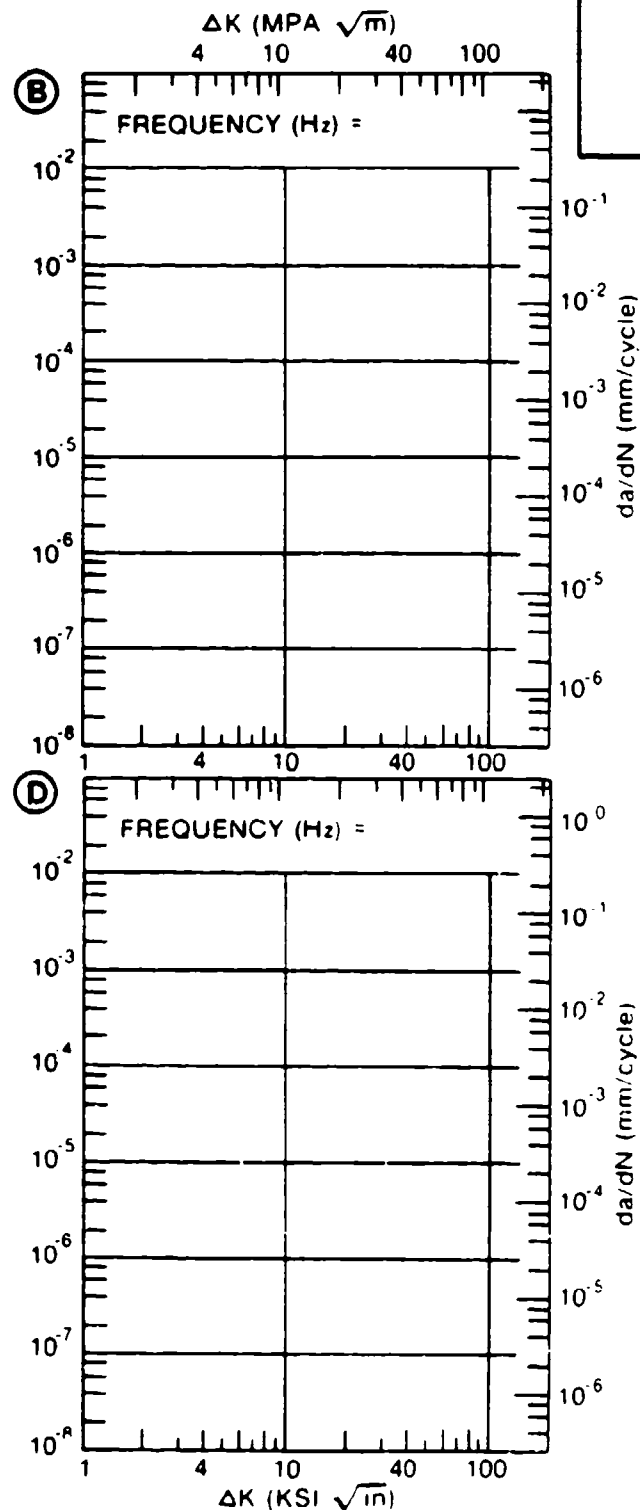
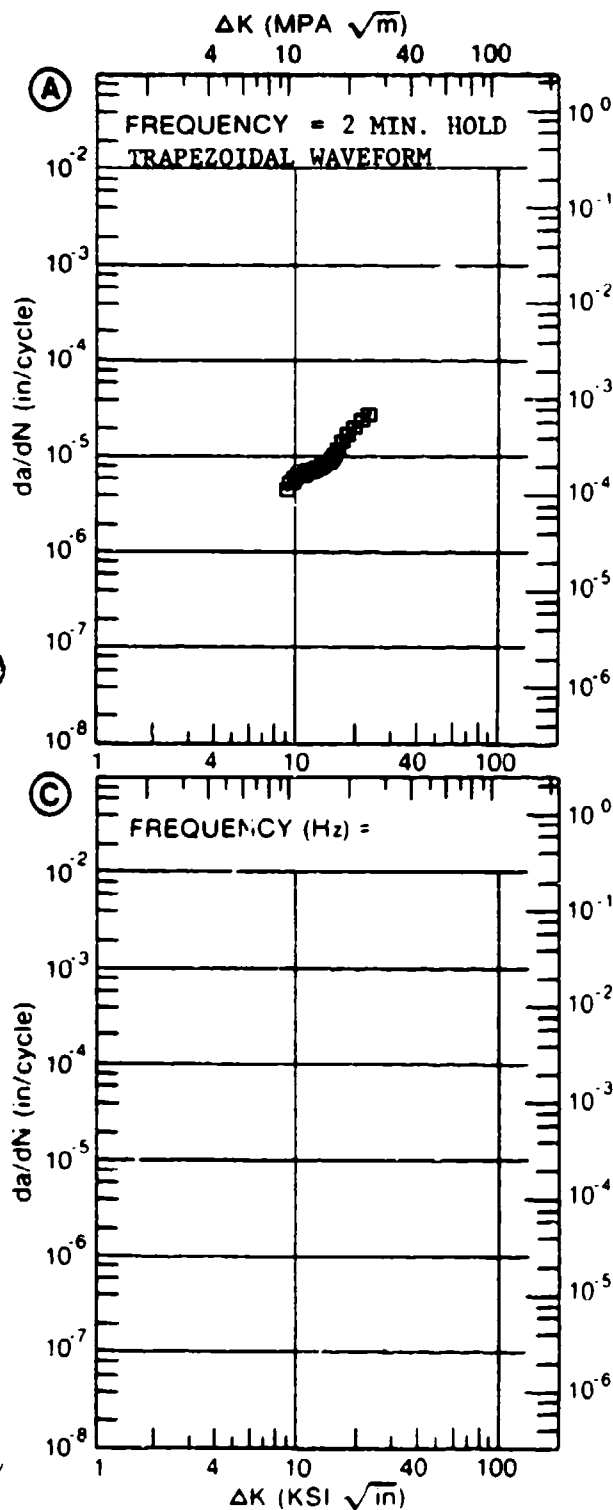


Figure 4.9.3.5

TABLE 4.10.1.1.1
 FATIGUE CRACK GROWTH RATE AT DIFFERENT LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM T1-6-2-4-6

TEST CONDITIONS

SPECIMEN ORIENTATION 1-1

ENVIRONMENT AIR AT 800 F

(IN)DIRECTION (1)	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
	EXTRUSION	0.10	20.00				1.69	10.1		
	EXTRUSION	0.30	20.00				2.09	12.3		
	EXTRUSION	0.50	20.00				3.11			
	EXTRUSION	0.70	20.00			0.81	3.42			

TABLE 4.10.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI 6-2-4-6

TEST CONDITIONS

SPECIMEN ORIENTATION C-R

ENVIRONMENT AIR AT 600 F

CONDITION/MT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2.5	5	10	20	50	100
1690F 2HRS AC. 1550F 2HRS OQ. 1100F 8HRS AC	FORGING	0.10	0.16							9.04
1690F 2HRS AC. 1550F 2HRS OQ. 1100F 8HRS AC	FORGING	0.10	30.00					1.41		
1690F 2HRS AC. 1550F 2HRS OQ. 1100F 8HRS AC	FORGING	0.50	0.16					3.80		
1690F 2HRS AC. 1550F 2HRS OQ. 1100F 8HRS AC	FORGING	0.50	2 MIN HOLD TIME TRAPEZOIDAL WAVEFORM							12.0

TABLE 4.10.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM Ti-6-2-4-6

TEST CONDITIONS

SPECIMEN
ORIENTATION C-RENVIRONMENT: AIR
AT 800 F

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5	5
				10	20
				50	100
1690F 2HRS AC. 1550F 2HRS OQ. 1100F 6HRS AC	FORGING	0.06	30.00		2.03
1690F 2HRS AC. 1550F 2HRS OQ. 1100F 6HRS AC	FORGING	0.10	0.16		11.5
1690F 2HRS AC. 1550F 2HRS OQ. 1100F 6HRS AC	FORGING	0.10	30.00		1.87
1690F 2HRS AC. 1550F 2HRS OQ. 1100F 6HRS AC	FORGING	0.50	0.16		4.67
1690F 2HRS AC. 1550F 2HRS OQ. 1100F 6HRS AC	FORGING	0.70	0.16		2.48
				2.48	6.71

TABLE 4.10.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.10.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6-2-4-6			
CONDITION:					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K	A: 7.20	.185			
MIN	B:				
	C:				
	D:				
	8.00	.291			
	9.00	.496			
	10.00	.819			
	13.00	2.65			
	16.00	5.25			
	20.00	9.70			
	25.00	22.0			
	30.00	48.0			
DELTA K	A: 33.04	61.9			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		21.73			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT:
 FORM: EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 147.2 KSI
 ULT. STRENGTH: 159.1 KSI
 SPECIMEN THK: 0.300"
 SPECIMEN WIDTH: 1.400"
 REFERENCES: UD001

TITAN.
 ALLOY
 TI-6-2-
 4-6

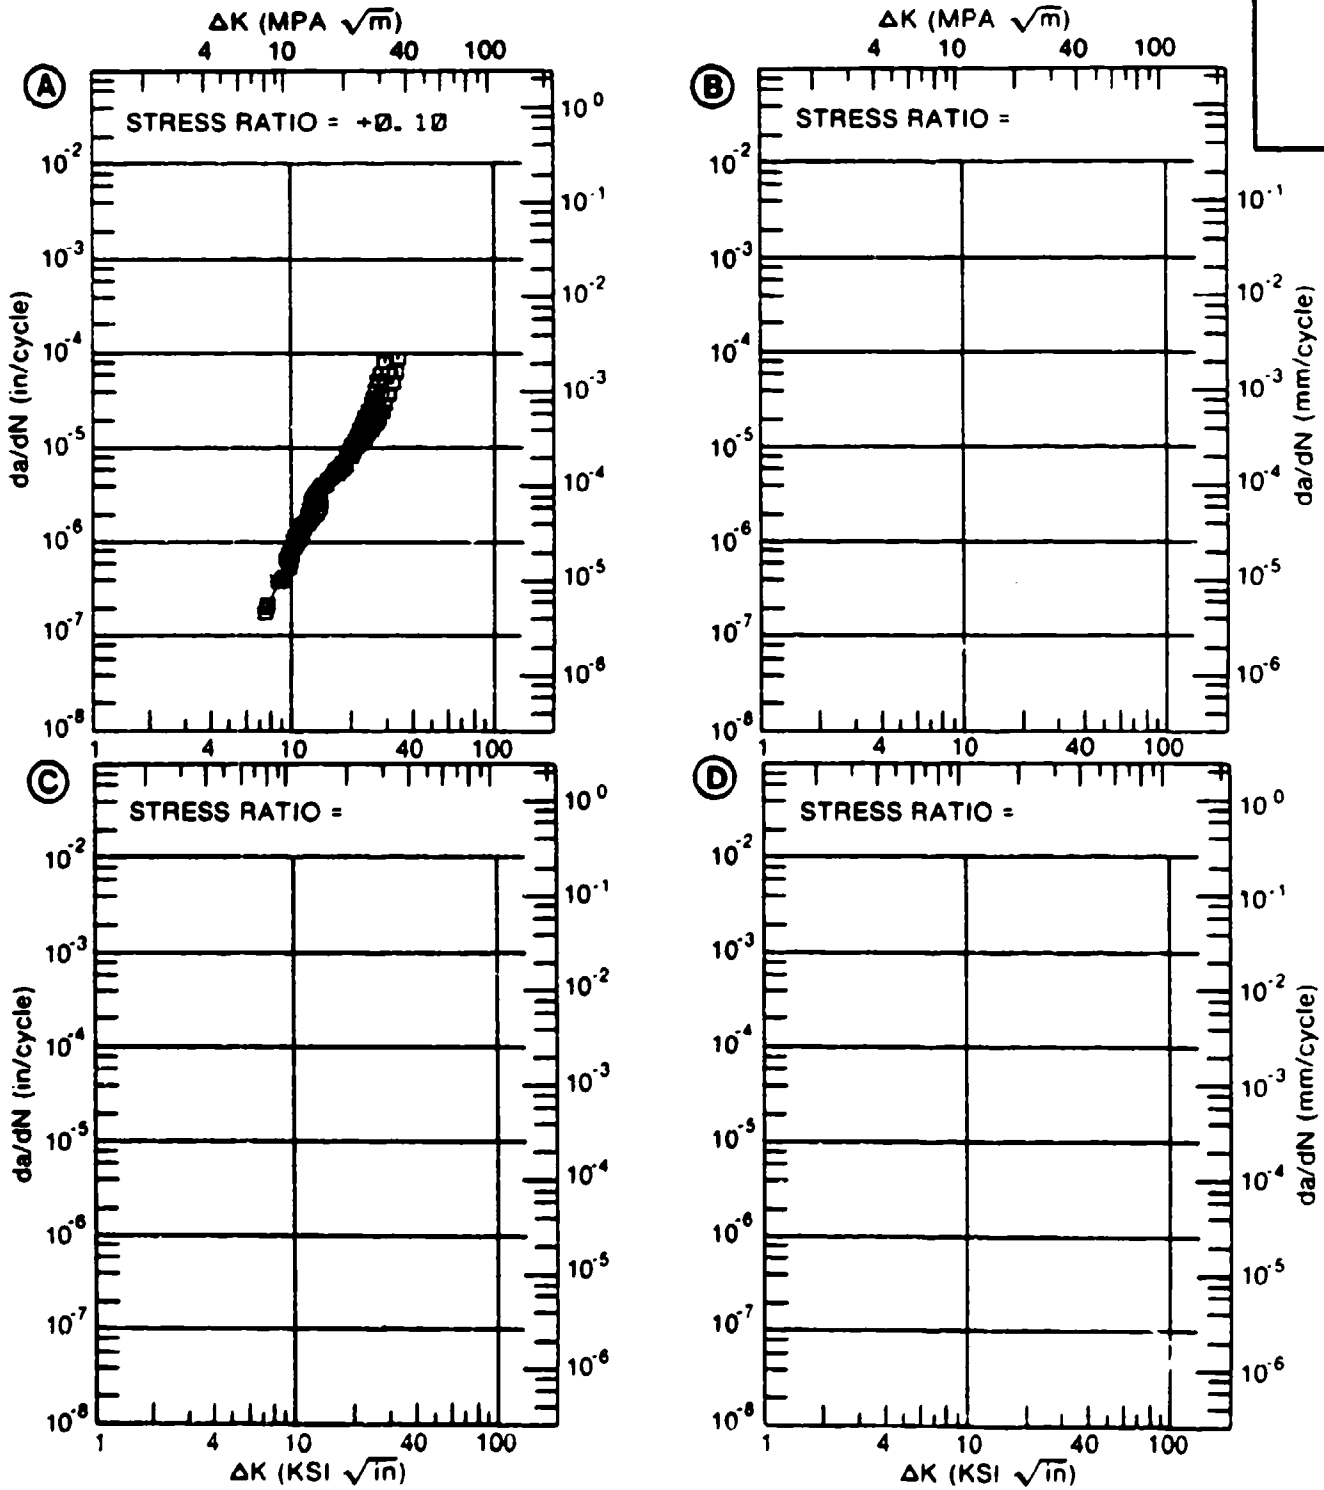


Figure 4.10.3.1

TABLE 4.10.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.10.3.2 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6-2-4-6			
CONDITION:					
ENVIRONMENT: + 800F. AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.30	R=+0.50	R=+0.70
DELTA K	A: 8.87	1.05			
MIN	B: 5.52		.654		
	C: 5.54			.861	
	D: 4.89				.815
	5.00				.819
	6.00		.747	.977	.976
	7.00		.984	1.31	1.31
	8.00		1.28	1.77	1.83
	9.00	1.14	1.65	2.37	2.53
	10.00	1.69	2.09	3.11	3.42
	13.00	3.27	3.96	6.30	6.81
	16.00	5.65	6.77	10.8	
	20.00	10.1	12.3		
	25.00	17.1	22.5		
	30.00	24.7	36.9		
	35.00		55.4		
DELTA K	A: 33.38	29.7			
MAX	B: 35.34		56.8		
	C: 19.33			16.9	
	D: 13.67				7.59
ROOT MEAN SQUARE		10.51	7.69	4.42	9.94
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT:
 FORM: EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: + 800° F. AIR

YIELD STRENGTH: 147.2 KSI
 ULT. STRENGTH: 159.1 KSI
 SPECIMEN THK: 0.300"
 SPECIMEN WIDTH: 1.400"
 REFERENCES: JUD001

TITAN.
 ALLOY

TI-6-2-
 4-6

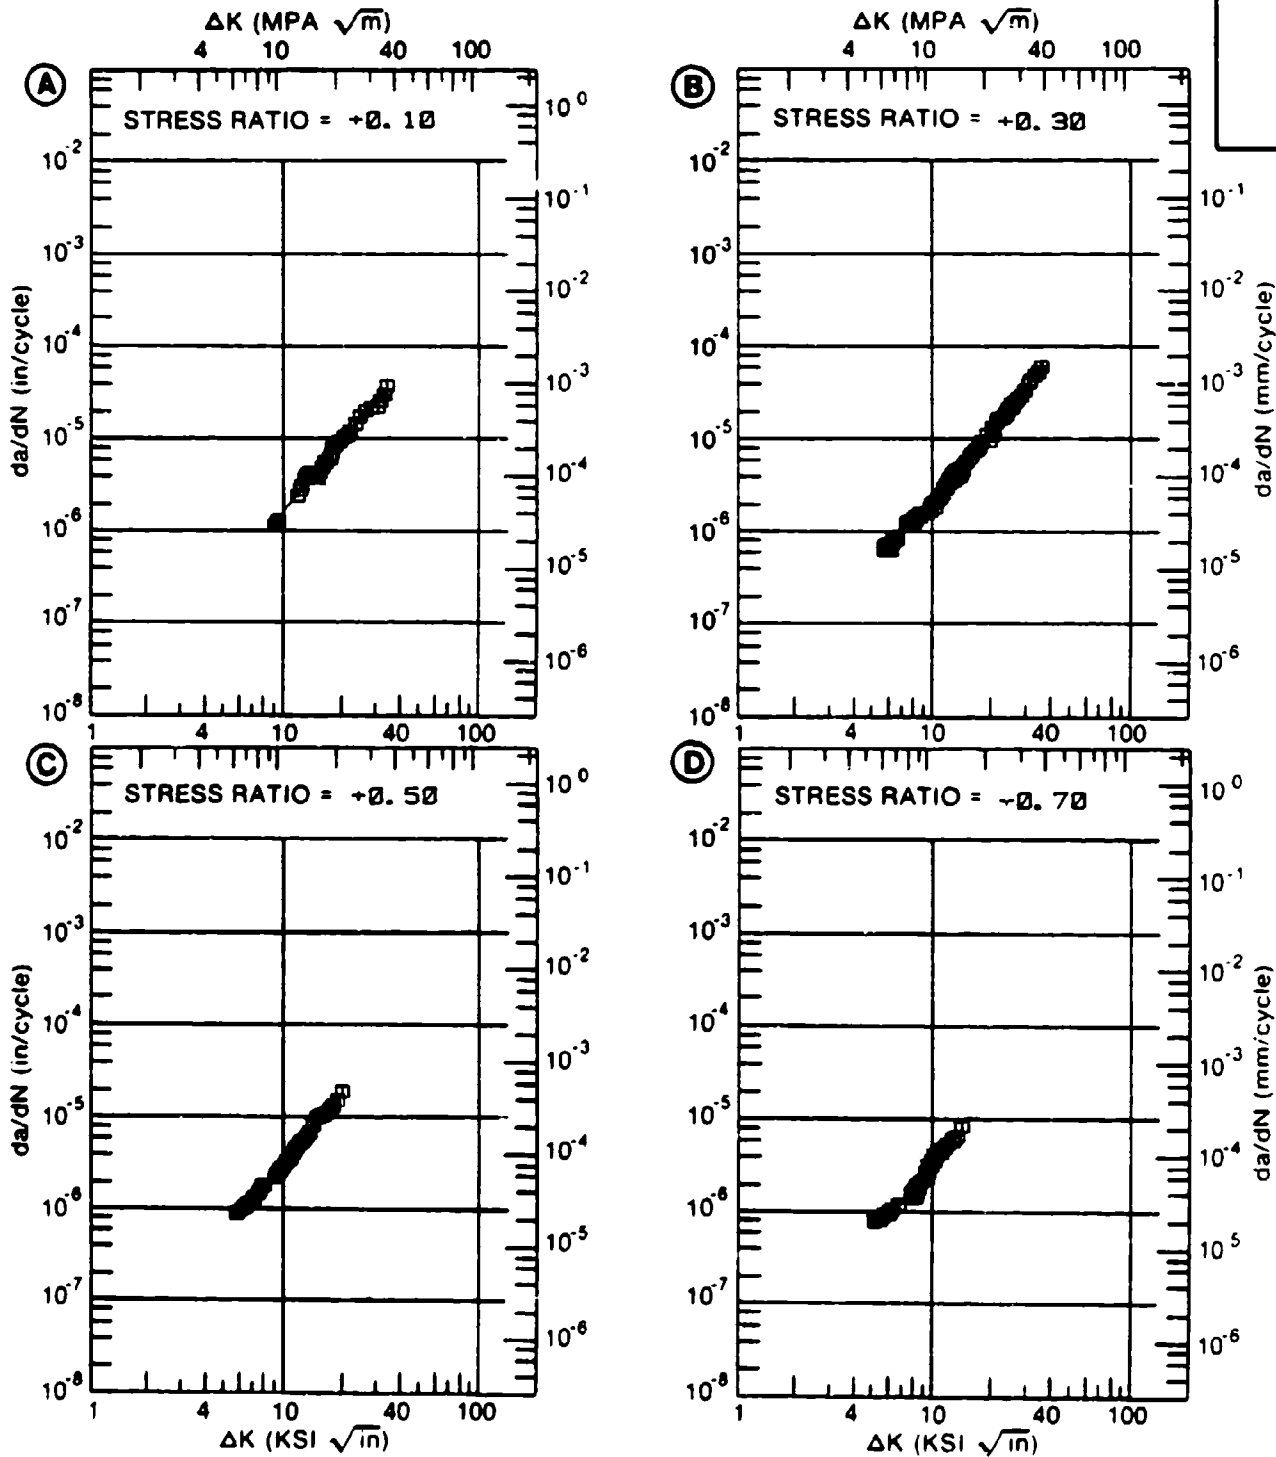


Figure 4.10.3.2

TABLE 4.10.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.10.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6-2-4-6
CONDITION: 1690F 2HRS AC, 1550F 2HRS OQ, 1100F 8HRS
AC

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN./CYCLE)			
	A	B	C	D
	E=+ 800F AIR			
DELTA K MIN	A: 5.05	.43		
	B: 6.00	.587		
	C: 7.00	.816		
	D: 8.00	1.12		
	9.00	1.52		
	10.00	2.03		
	13.00	4.36		
DELTA K MAX	A: 14.76	6.43		
	B:			
	C:			
	D:			

ROOT MEAN SQUARE 5.79
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1800F 2HRS AC, 1550F 2HRS OQ, 1100F 8HRS AC
 FORM: 1.00" TH FORGING YIELD STRENGTH: 185.5 KSI
 SPECIMEN TYPE: CCP ULT. STRENGTH: 180.8 KSI
 ORIENTATION: C-R SPECIMEN THK: 0.077"
 STRESS RATIO: +0.08 SPECIMEN WIDTH: 1.750"
 FREQUENCY: 30.00 HZ REFERENCES: PW002

TITAN.
ALLOY

TI-6-2-
4-8

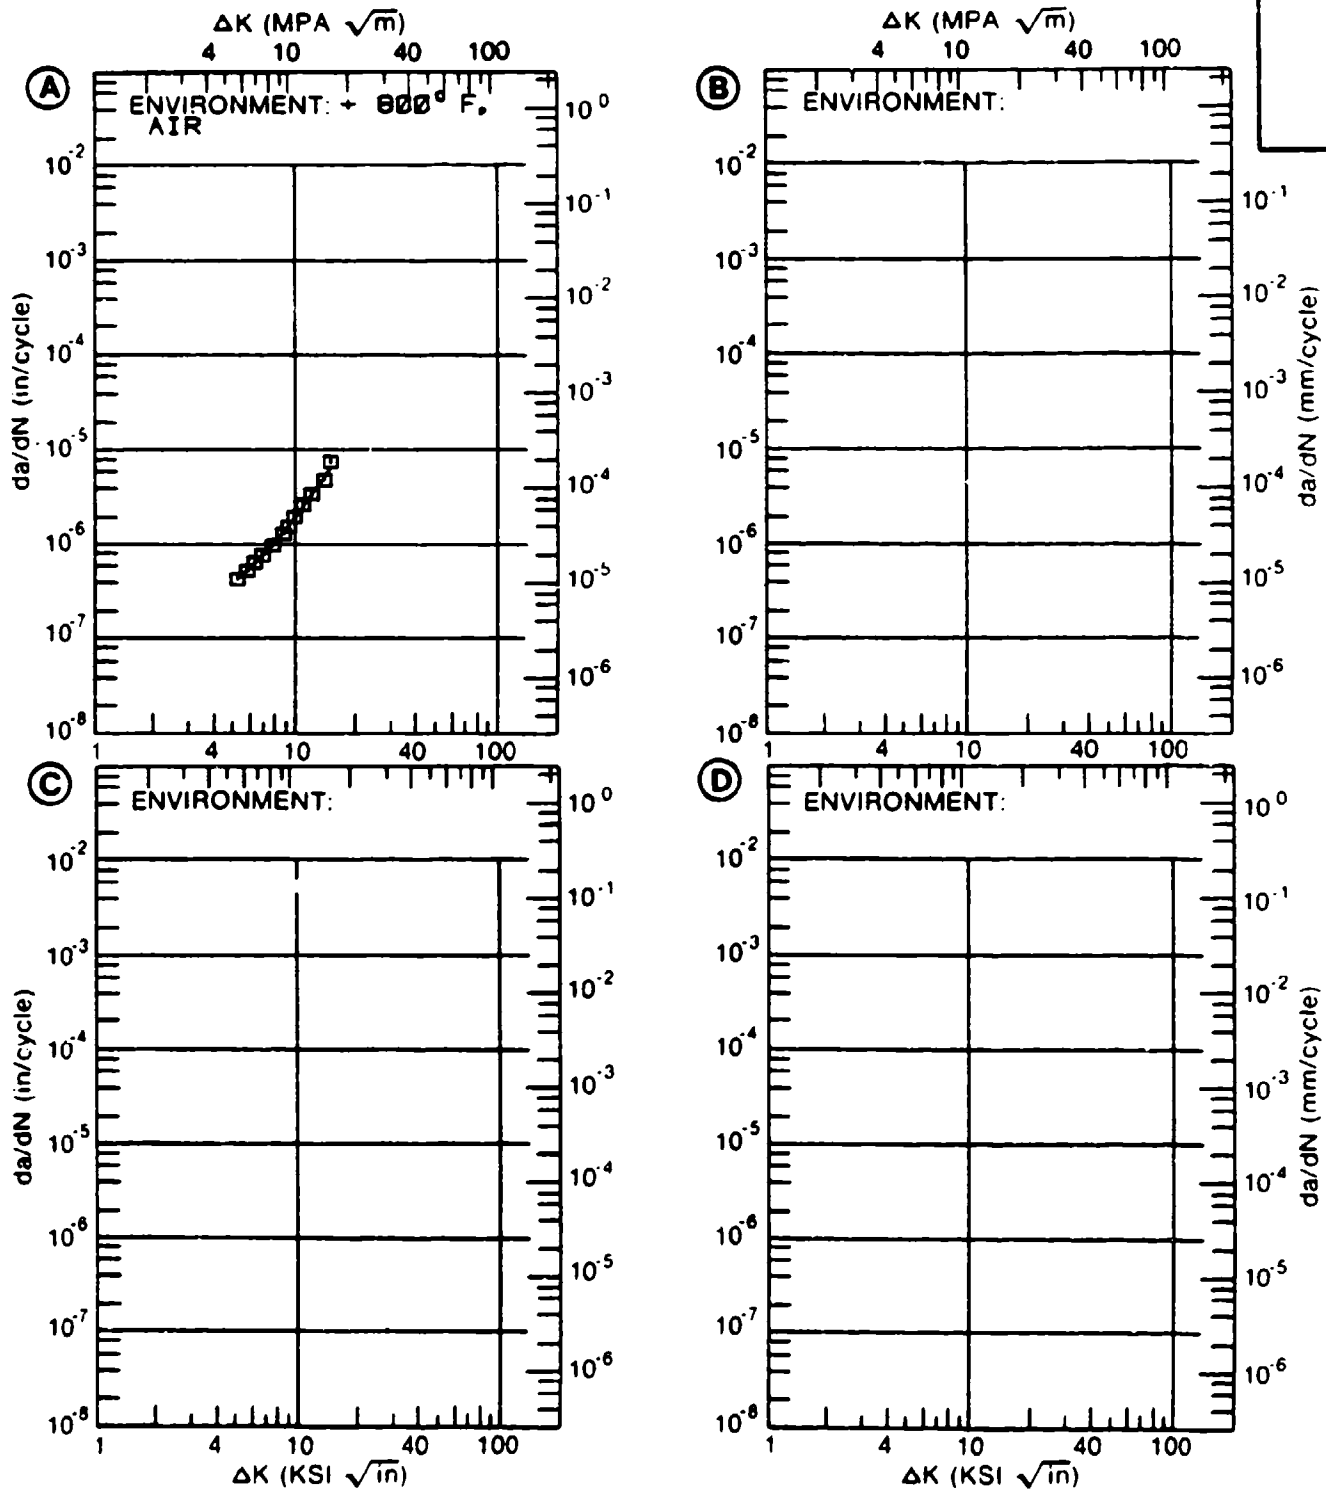


Figure 4.10.3.3

TABLE 4.10.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.10.3.4 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6-2-4-6			
CONDITION: 1690F 2HRS AC, 1550F 2HRS OG, 1100F 8HRS AC					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E=+ 600F AIR			
DELTA K	A: 13.85	4.87			
MIN	B:				
	C:				
	D:				
	16.00	7.10			
	20.00	12.0			
	25.00	19.6			
	30.00	29.6			
	35.00	43.1			
	40.00	61.6			
DELTA K	A: 47.39	103.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		8.21			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: 1690F 2HRS AC, 1550F 2HRS OQ, 1100F 8HRS AC
 FORM: 1.80" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 STRESS RATIO: +0.50
 FREQUENCY: 2 MIN. HOLDTIME
 TRAPEZOIDAL WAVEFORM

YIELD STRENGTH: 165.5 KSI
 ULT. STRENGTH: 180.8 KSI
 SPECIMEN THK: 0.074"
 SPECIMEN WIDTH: 1.750"
 REFERENCES: PW002

TITAN.
ALLOY

TI-6-2-
4-6

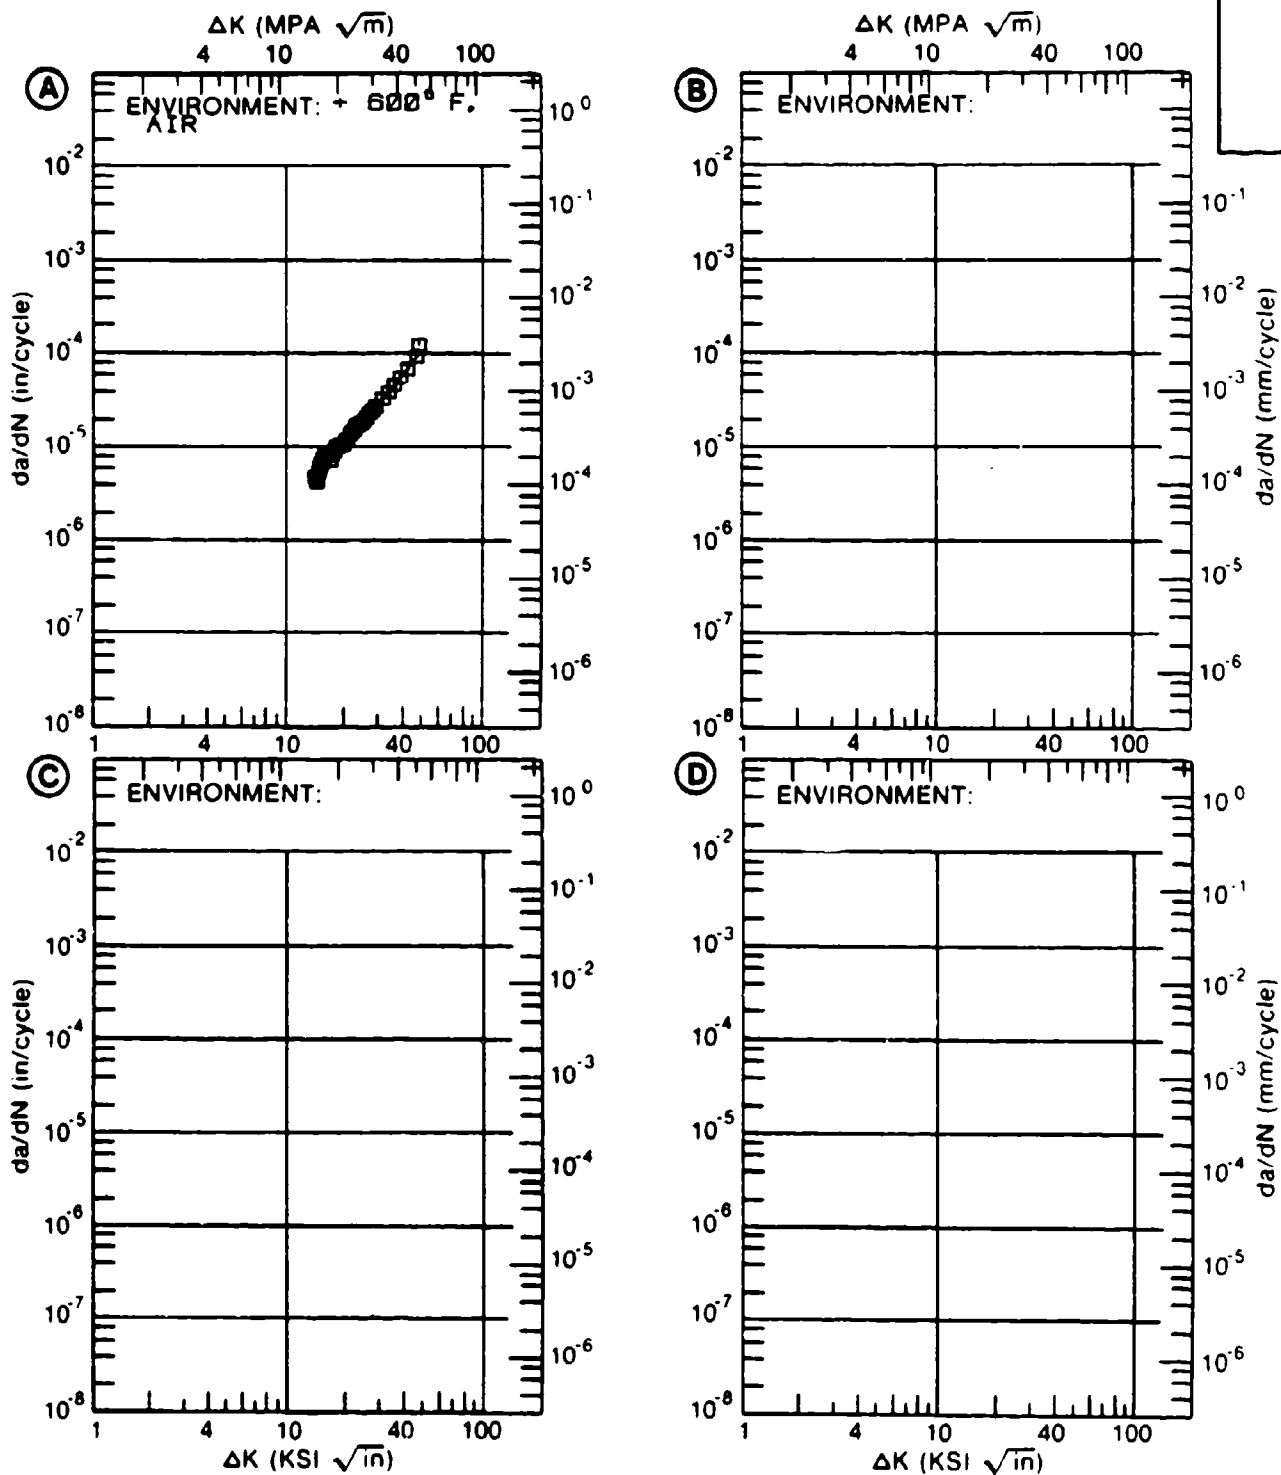


Figure 4.10.3.4

TABLE 4.10.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.10.3.5 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6-2-4-6			
CONDITION: 1690F 2HRS AC, 1550F 2HRS OQ, 1100F 8HRS AC					
DELTA K (KBI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E → 800F			
		AIR			
DELTA K	A: 4.73	2.46			
MIN	B:				
	C:				
	D:				
	5.00	2.48			
	6.00	2.81			
	7.00	3.43			
	8.00	4.31			
	9.00	5.40			
	10.00	6.71			
	13.00	11.6			
DELTA K	A: 14.43	14.3			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		5.34			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: 1800F 2HRS AC, 1550F 2HRS OQ, 1100F 8HRS AC
 FORM: 1.00" TH FORGING YIELD STRENGTH: 185.5 KSI
 SPECIMEN TYPE: CCP ULT. STRENGTH: 180.8 KSI
 ORIENTATION: C-R SPECIMEN THK: 0.083"
 STRESS RATIO: +0.70 SPECIMEN WIDTH: 1.750"
 FREQUENCY: 0.16 HZ REFERENCES: PW002

TITAN.
ALLOY

TI-6-2-
4-6

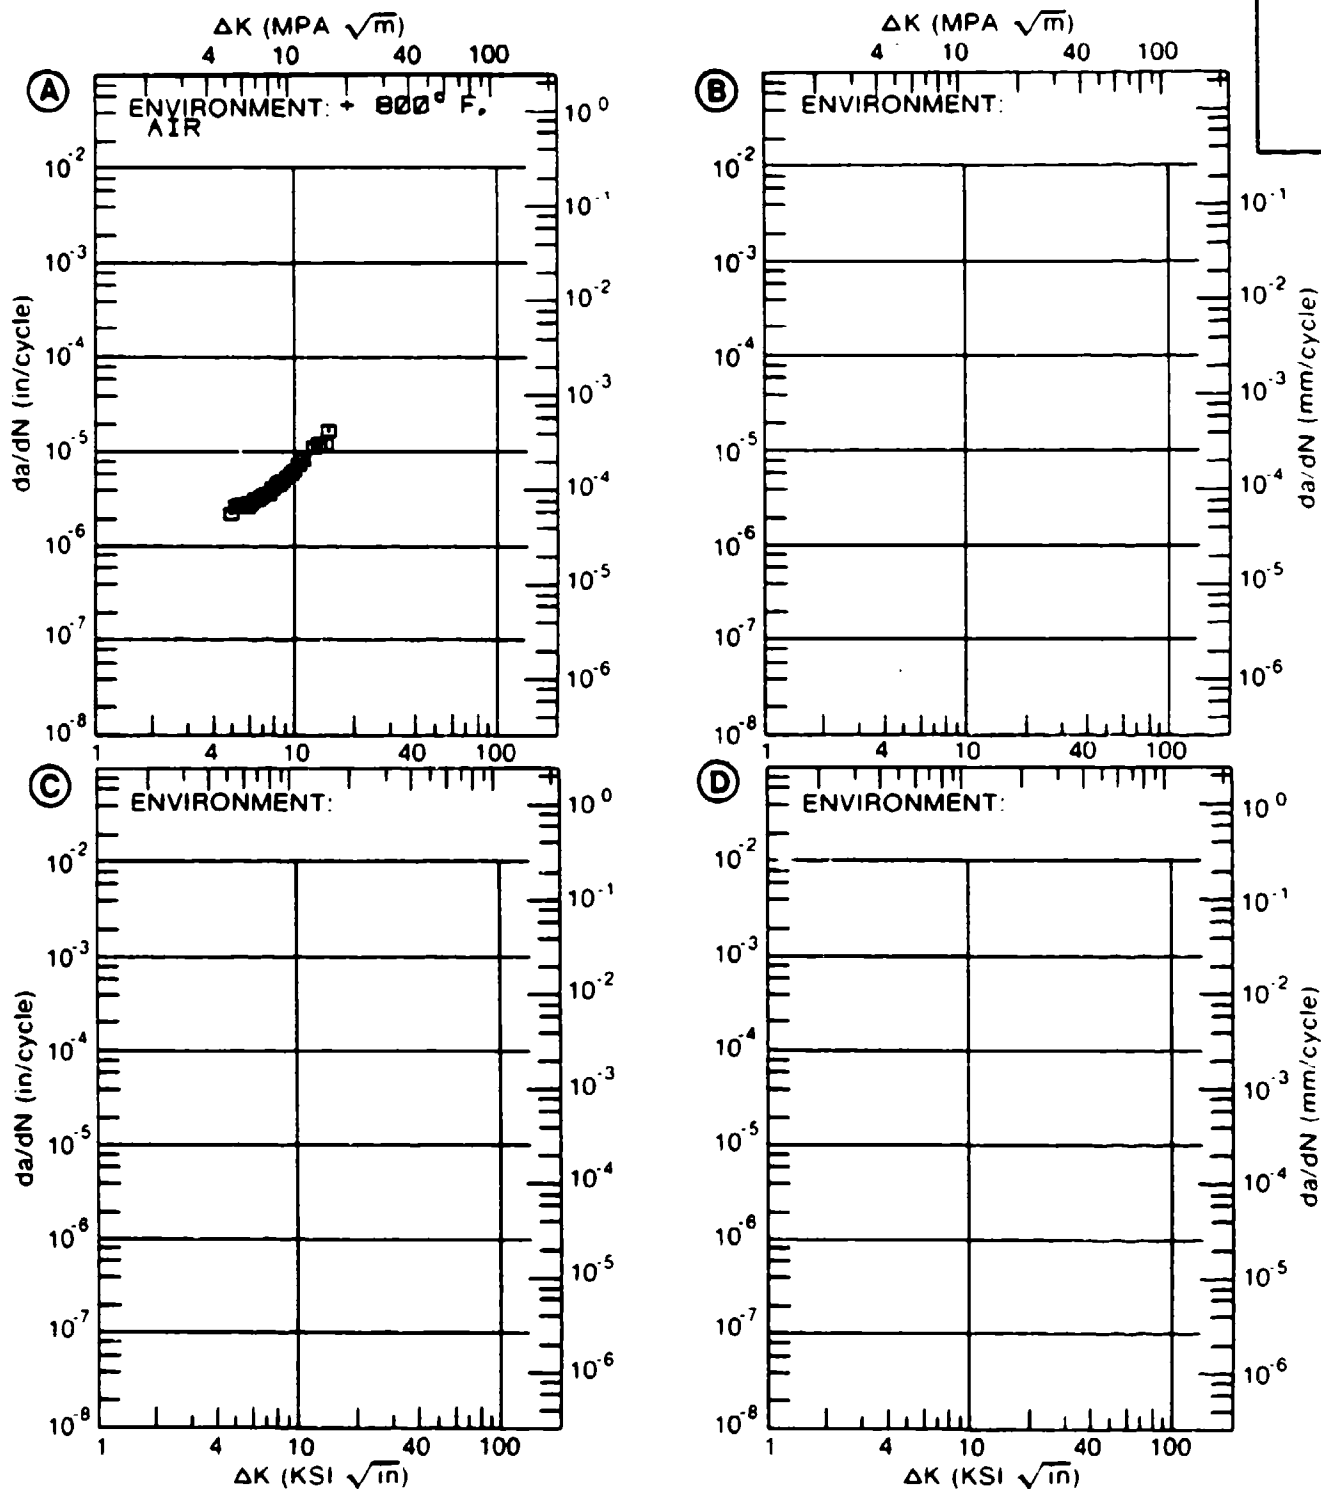


Figure 4.10.3.5

TABLE 4.10.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.10.3.6 INDICATING EFFECT
OF ENVIRONMENT

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E=+ 600F AIR	E=+ 800F AIR	
DELTA K	A: 4.87	.09			
MIN	B: 8.23		.71		
	C: 8.51			1.09	
	D:				
	5.00	.105			
	6.00	.185			
	7.00	.314			
	8.00	.496			
	9.00	.718	.991	1.36	
	10.00	.985	1.41	1.87	
	13.00	2.44	3.20	3.49	
	16.00		6.41	7.28	
DELTA K	A: 14.06	5.88			
MAX	B: 17.43		8.91		
	C: 17.28			11.0	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		5.96	3.55	6.28	
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: 1600F 2HRS AC, 1550F 2HRS OQ, 1100F 8HRS AC
 FORM: 2.80" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 STRESS RATIO: +0.10
 FREQUENCY: 30.00 HZ

YIELD STRENGTH: 186.0 KSI
 ULT. STRENGTH: 182.3 KSI
 SPECIMEN THK: 0.078- 0.082"
 SPECIMEN WIDTH: 1.750"
 REFERENCES: PW002

TITAN.
 ALLOY

TI-6-2-
 4-6

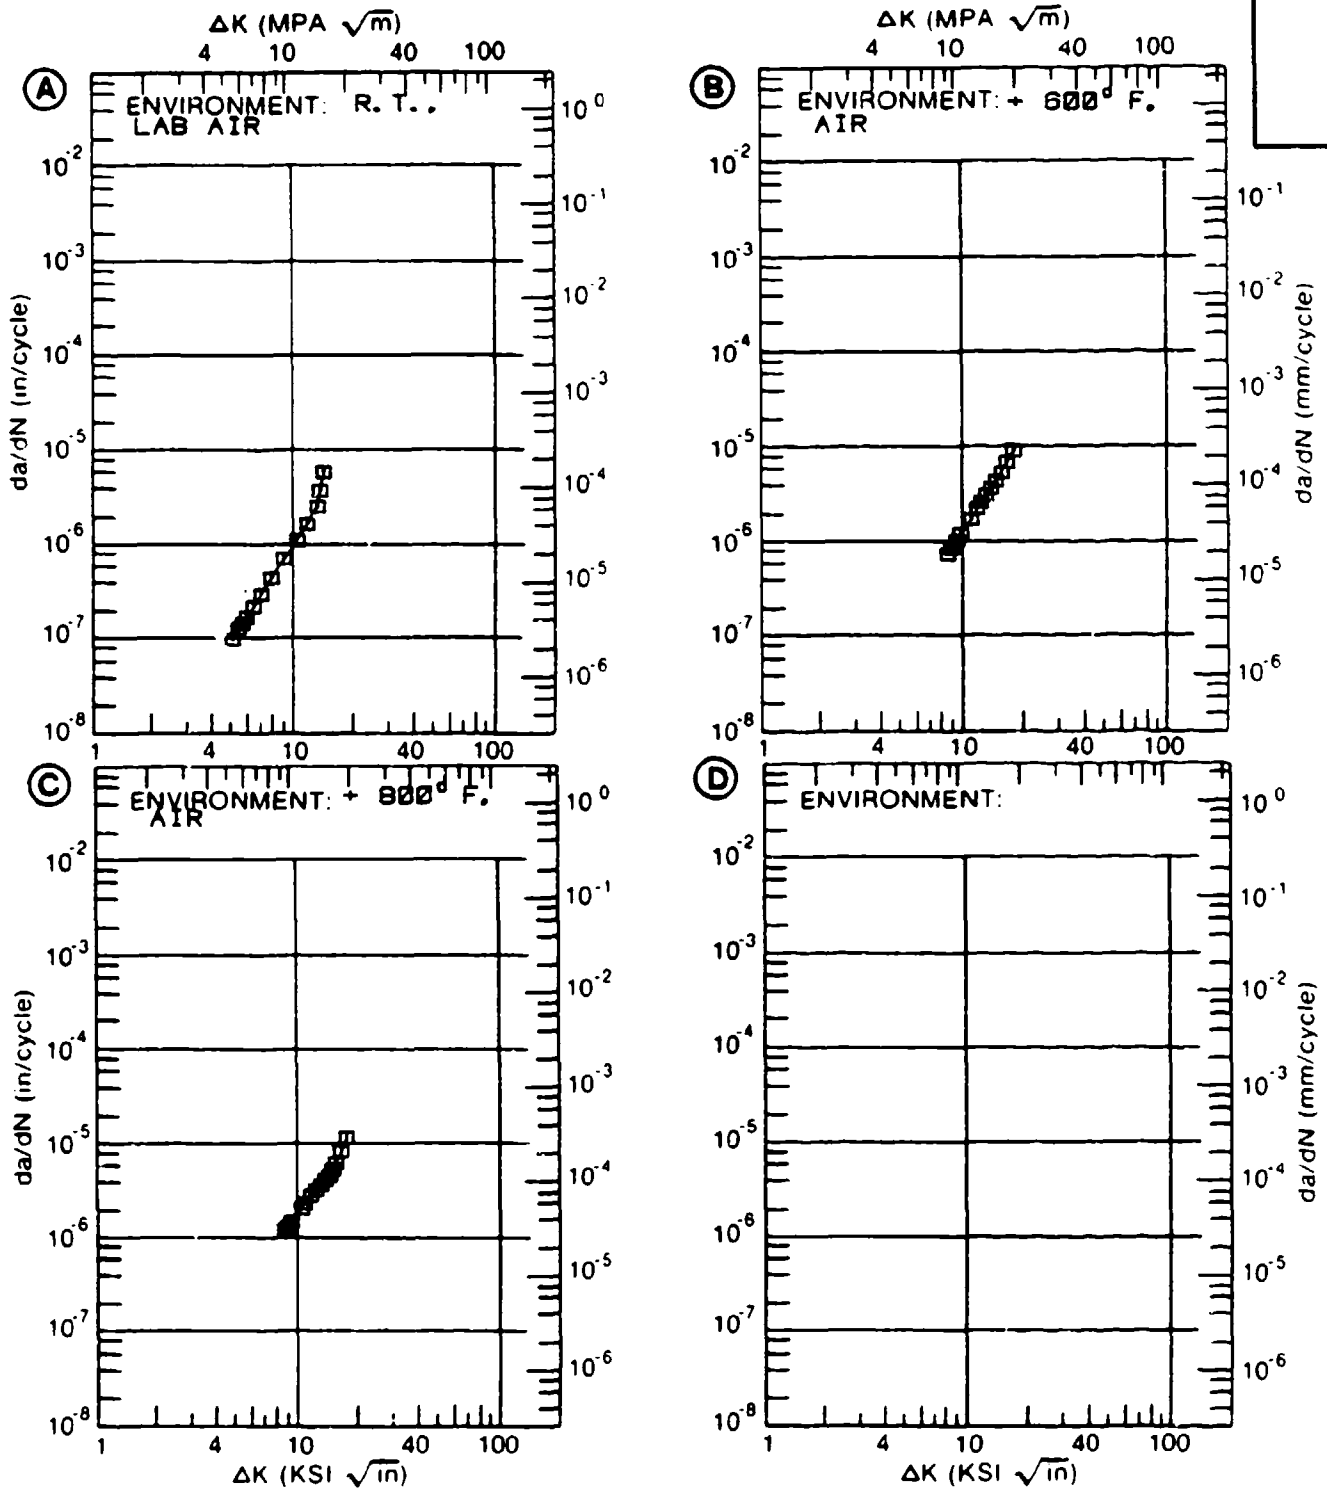


Figure 4.10.3.6

TABLE 4.10.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.10.3.7 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6-2-4-6			
CONDITION: 1690F 2HRS AC, 1550F 2HRS OG, 1100F 8HRS AC					
DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN./CYCLE)			
		A	B	C	D
		E==+ 600F	E==+ 800F		
		AIR	AIR		
DELTA K	A: 10.60	1.71			
MIN	B: 13.03		4.20		
	C:				
	D:				
	13.00	2.58			
	16.00	4.56	6.96		
	20.00	9.04	11.5		
	25.00	17.6	18.9		
	30.00	28.0	29.3		
	35.00		44.4		
DELTA K	A: 32.52	33.1			
MAX	B: 39.00		61.4		
	C:				
	D:				
ROOT MEAN SQUARE		12.22	7.08		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: 1000F 2HRS AC, 1550F 2HRS OQ, 1100F 8HRS AC
 FORM: 2.00" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 STRESS RATIO: +0.10
 FREQUENCY: 0.16 HZ

YIELD STRENGTH: 186.0 KSI
 ULT. STRENGTH: 192.3 KSI
 SPECIMEN THK: 0.079- 0.081"
 SPECIMEN WIDTH: 1.750"
 REFERENCES: PW002

TITAN.
 ALLOY

TI-6-2-
 4-6

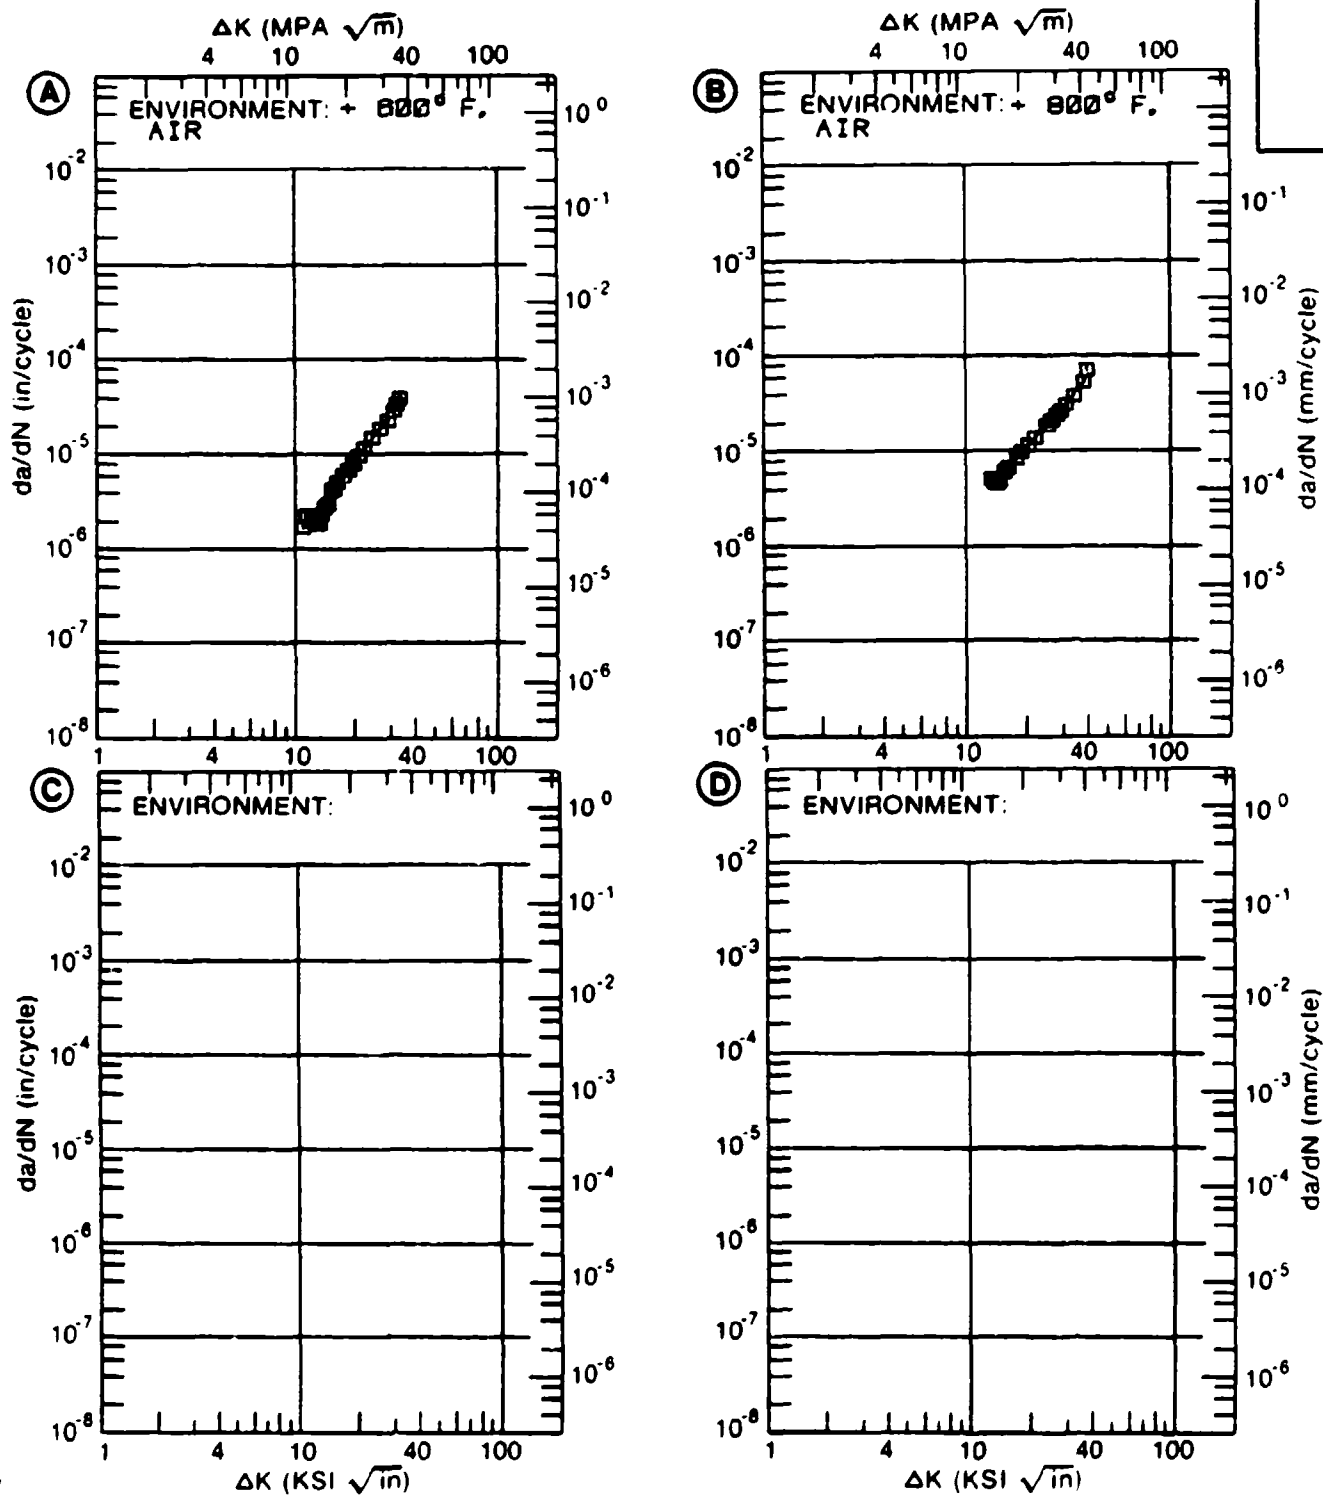


Figure 4.10.3.7

TABLE 4.10.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.10.3.8 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6-2-4-6
CONDITION: 1690F 2HRS AC, 1550F 2HRS OG, 1100F 8HRS
AC

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E=+ 600F AIR	E=+ 800F AIR		
DELTA K A:	7.88	1.35			
MIN B:	8.16		3.26		
C:					
D:					
	8.00	1.51			
	9.00	2.80	3.82		
	10.00	3.80	4.67		
	13.00		8.96		
	16.00		18.1		
DELTA K A:	12.83	7.75			
MAX B:	16.58		20.9		
C:					
D:					
ROOT MEAN SQUARE		6.25	4.12		
PERCENT ERROR					

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1800F 2HRS AC, 1550F 2HRS OQ, 1100F 8HRS AC
 FORM: 2.80" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 STRESS RATIO: +0.50
 FREQUENCY: 0.16 HZ

YIELD STRENGTH: 186.0 KSI
 ULT. STRENGTH: 182.3 KSI
 SPECIMEN THK: 0.080- 0.081"
 SPECIMEN WIDTH: 1.750"
 REFERENCES: PW002

TITAN.
 ALLOY
 TI-8-2-
 4-6

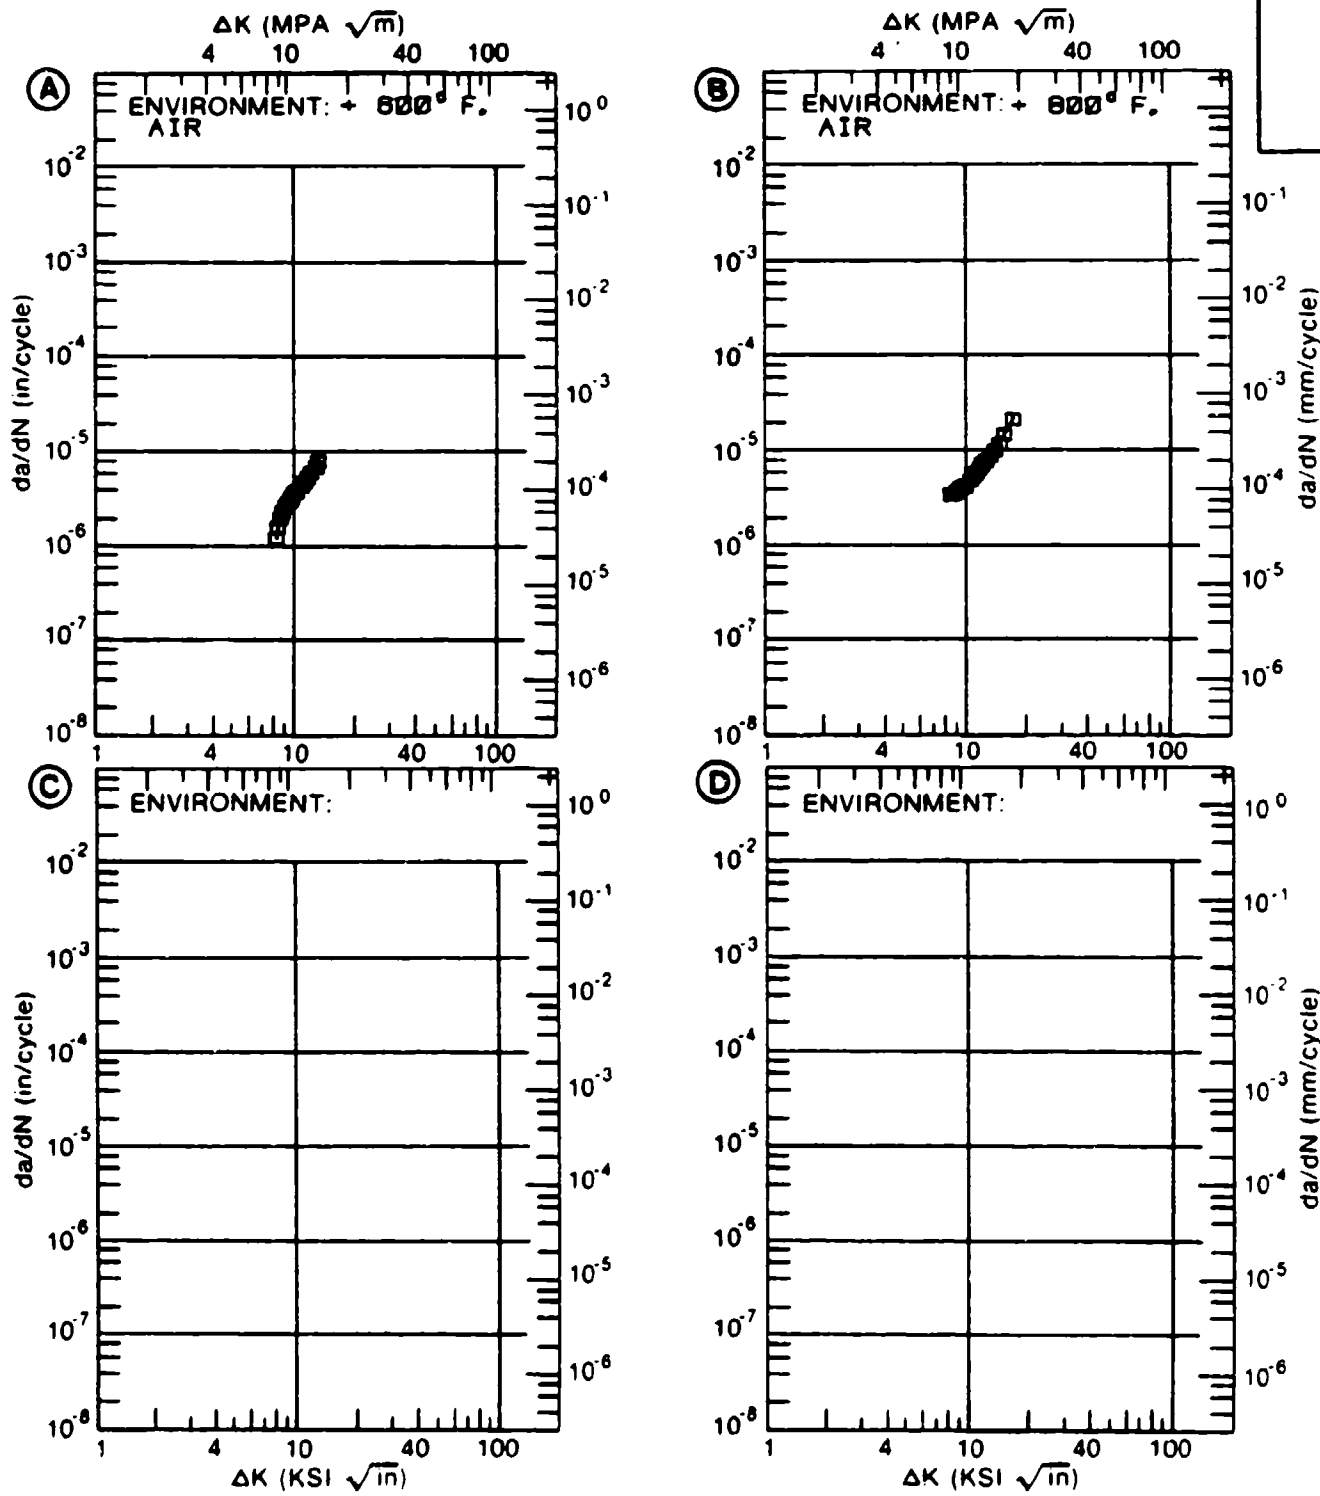


Figure 4.10.3.8

TABLE 4.10.3.9

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.10.3.9 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6-2-4-6			
CONDITION: 1690F 2HRS AC, 1550F 2HRS OQ, 1100F 8HRS AC					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR . 16HZ	E= R. T. LAB AIR 999. 99HZ	E=+ 600F AIR . 16HZ	
DELTA K MIN	A: 3. 89	. 31			
	B: 1. 86		. 00		
	C: 4. 41			. 79	
	D:				
	2. 00		. 0130		
	2. 50		. 0636		
	3. 00		. 121		
	3. 50		. 176		
	4. 00	. 317	. 237		
	5. 00	. 524	. 460	1. 12	
	6. 00	1. 53		1. 65	
	7. 00	4. 73		2. 18	
	8. 00	12. 2		2. 80	
	9. 00			3. 61	
	10. 00			4. 74	
	13. 00			12. 5	
DELTA K MAX	A: 8. 59	18. 9			
	B: 5. 84		1. 48		
	C: 14. 50			22. 0	
	D:				
ROOT MEAN SQUARE		12. 54	20. 47	7. 74	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0. 0-0. 5 0. 5-0. 8 0. 8-1. 25 1. 25-2. 0 >2. 0				

CONDITION/HT: 1800F 2HRS AC, 1550F 2HRS OQ, 1100F 8HRS AC
 FORM: 2.80" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 STRESS RATIO: +0.70
 FREQUENCY:
 YIELD STRENGTH: 186.0 KSI
 ULT. STRENGTH: 182.9 KSI
 SPECIMEN THK: 0.079- 0.081"
 SPECIMEN WIDTH: 1.750"
 REFERENCES: PW002

TITAN.
ALLOY

TI-6-2-
4-8

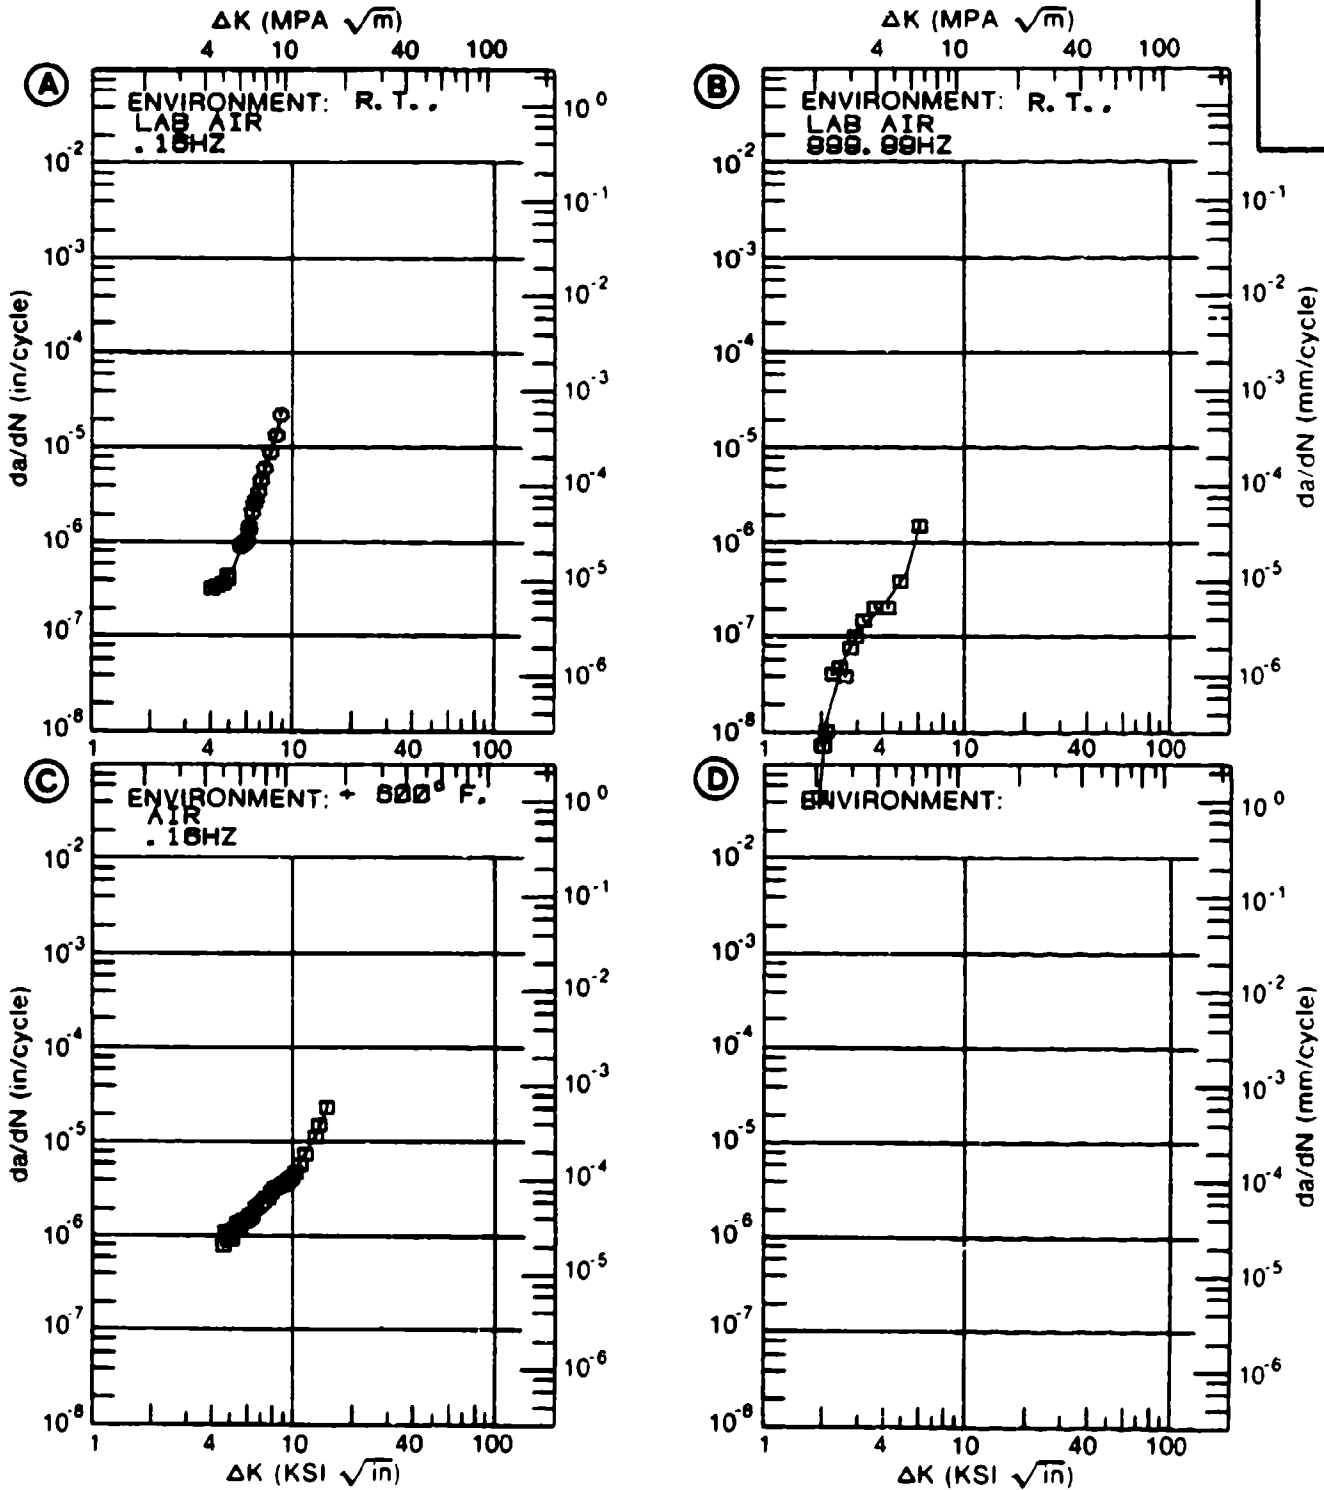


Figure 4.10.3.9

TABLE 4.11.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
TITANIUM ALLOY TI-6AL-4V AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI BURTIN) DEVIATION		(NUMBER OF SPECIMENS)	
	L-I	H-I	L-I	H-I
ANNEALED 1375F 3HR. AC	60.4 ± 5.9 (2)	---	---	---
BETA PROCESSED MILL ANNEALED	94.9 ± 4.8 (3)	---	---	---
MILL ANNEAL	55.6 ± 1.3 (2)	---	---	---
MILL ANNEALED	---	100.6 ± 6.8 (6)	---	---
RECRYSTALLIZE ANNEAL	82.8 ± 7.8 (22)	80.8 ± 10.8 (22)	---	---
STA	---	42.6 ± 2.0 (3)	---	---
1750F 1HR FC TO 1100F. AC	---	91.5 ± 2.1 (2)	---	---
1750F 1HR. FC TO RT	71.8 ± 3.2 (2)	91.6 ± 1.3 (2)	---	---
1750F 2HR. HB. 1000F 2HR. AC. 1300F 2HR. AC. STA	41.4 ± 2.3 (2)	---	---	---
FORGING				
CONDITON/HT	L-I	H-I	L-I	H-I
AS FORGED-NA ALPHA-BETA FORGED. MILL ANNEALED	---	35.4 ± 2.7 (4)	---	---
ANNEALED	84.4 ± 1.8 (2)	83.4 ± 9.9 (2)	---	---
ANNEALED 1300F 4 HR. AC	58.1 ± 1.2 (3)	62.2 ± 3.0 (3)	68.1 ± 1.0 (2)	---

TABLE 4.11.1.1 (con't)

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
TITANIUM ALLOY TI-6AL-4V AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION		(NUMBER OF SPECIMENS)	
	L-I	I-I	L-I	I-I
B FORGED-FA BETA FORGED, MILL ANNEALED 1300F 2 HR. AC	70.6 ± 4.9 (3)	71.0 ± 0.4 (3)	73.9 ± 2.5 (2)	
	47.7 ± 2.9 (3)	49.9 ± 3.9 (3)	43.6 ± 9.8 (3)	
	83.6 ± 9.9 (41)	83.9 ± 6.9 (50)	86.9 ± 3.2 (9)	
RECRYSTALLIZE ANNEAL	79.9 ± 4.2 (6)	81.2 ± 9.8 (6)	---	---
	---	79.3 ± 4.9 (3)	---	---
1700F 6 HR. AC, 1400F 6 HR. AC	---	---	---	---
	---	---	---	---
1750F 1 HR. WD, 1000F 4 HR	---	---	---	---
	---	---	---	---
CONDITION/HT	EXTENSION			
	L-I	I-I	L-I	I-I
ANNEALED	---	73.3 ± 2.3 (2)	---	---
MILL ANNEALED	83.9 ± 3.1 (9)	87.5 ± 4.1 (6)	---	---
CONDITION/HT	FORGED BAR			
	L-I	I-I	L-I	I-I
AS RECEIVED	97.1 ± 10.4 (14)	94.9 ± 10.8 (21)	---	---
B FORGED BETA FORGED REHEATED TO 1950F DRAIN TO SIZE, ANNEALED 1300F	---	42.6 ± 4.3 (4)	---	---

TABLE 4.11.1.1 (con't)
 MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
 TITANIUM ALLOY T1-6AL-4V AT ROOM TEMPERATURE

CONDITION/MT	MEAN K _{IC} ± STANDARD DEVIATION		NUMBER OF SPECIMENS
	(KSI)	(BART(IN))	
	BILLEI		
	L-I	I-I	B-I
ANNEALED	79.6 ± 9.6 (2)	---	---
ANNEALED 1000F 2 HR. AC	50.9 ± 0.6 (2)	---	---
DIFFUSION BOND ANNEALED	68.2 ± 9.7 (9)	64.2 ± 11.8 (13)	---
MILL ANNEALED 1300F 2 HR. AC	84.0 ± 3.4 (3)	---	---

TABLE 4.11.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: DRY AIR AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
BA	PLATE	0.10	6.00		0.22 9.19
BA	PLATE	0.10	6.00		0.06 5.42 85.6
BA	PLATE	0.30	6.00		0.30 9.75
BA	PLATE	0.50	6.00		1.19 10.9
<hr/>					
BETA PROCESSED -MILL ANNEALED	SHEET	0.10	10.00		48.8
BETA PROCESSED -MILL ANNEALED	PLATE	0.10	10.00		4.51
BETA PROCESSED -MILL ANNEALED	PLATE	0.10	10.00		48.7
BETA PROCESSED -MILL ANNEALED	PLATE	0.10	10.00		4.66

TABLE 4.11.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONSSPECIMEN
ORIENTATION L-TENVIRONMENT: L.H.A.
AT R.T.

CONDITION/MT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)				
					2.5	5	10	20	50
DBTC	PLATE	0.08	1.00					16.4	750
DBTC	PLATE	0.30	1.00	SPEC THK=1.00"			0.35	13.1	265
DBTC	PLATE	0.30	1.00	SPEC THK=0.50"			0.62	19.4	2180
MA	SHEET	0.08	6.00				1.79	13.7	
MA	SHEET	0.30	6.00				2.24		
MA	SHEET	0.50	6.00				2.30	21.1	
MA	PLATE	0.30	1.00	DATA OUT OF TREND				<u>72.6</u>	
MA	PLATE	0.30	1.00- 6.00				0.42	24.7	402
MA	PLATE	0.30	1.00- 6.00				0.46	11.2	255
MA	EXTRUSION	0.08	1.00				0.37	11.7	
MA	EXTRUSION	0.08	6.00					16.8	
MA	EXTRUSION	0.30	6.00					17.3	
MA	EXTRUSION	0.50	6.00						
RA	PLATE	0.08	6.00					10.4	
RA	PLATE	0.08	6.00					7.80	
RA	PLATE	0.08	6.00	DATA OUT OF TREND				<u>3.34</u>	145
RA	PLATE	0.08	6.00				0.72	11.3	

TABLE 4.11.1.3 (Con't)

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: L.H.A.
AT R.T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	2.5	5	10	20	50	100
RA	PLATE	0.08	6.00				0.49	9.42	171	
RA	PLATE	0.30	6.00				1.39	15.9		
RA	PLATE	0.50	6.00				1.94	16.8		
RA	PLATE	0.70	6.00				3.12			
RA	FORGING	0.08	1.00				0.38	5.78	166	
RA	FORGING	0.08	6.00					6.76		
RA	FORGING	0.30	6.00				1.22	16.2	324	

TABLE 4.11.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT LAB AIR AT R.T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
ANNEALED	BILLET	0.02	10 00-20.00		0.27 9.49
ANNEALED AT 1375F. 3HRS. AC	PLATE	0.02	10 00-20.00		0.28 9.70
SA	FORGING	0.02	0.10-20.00		2.55 102
BETA PROCESSED -MILL ANNEALED	PLATE	0.10	1.00		0.91
BETA PROCESSED MILL ANNEALED	PLATE	0.50	1.00		1.47
MA	PLATE	-1.00	10.00		1.14 12.8 328
MA	PLATE	0.02	0.10-30.00	DATA OUT OF TREND	0.01 0.44 (12.4)
MA	PLATE	0.02	0.10-30.00		0.15 5.92
MA	PLATE	0.04	20.00		96.5
MA	PLATE	0.05	20.00		6.97
MA	PLATE	0.30	20.00		0.99
MA	PLATE	0.50	10.00		8.52 92.4
MA	FORGING	0.02	1.00-30.00		8.18 292

TABLE 4.11.1.5
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN ORIENTATION L-T ENVIRONMENT: H.H.A. AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
BA	PLATE	0.10	0.10		4.10 115
BA	PLATE	0.30	0.10		9.31
BA	PLATE	0.50	0.10		12.0 1009

TABLE 4.11.1.6

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM T1-6AL-4V

TEST CONDITIONS

SPECIMEN
ORIENTATION L-TENVIRONMENT: J.P. 4
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	2.5	5	10	20	30	50	100
FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)											
BA	FORGING	0.02	0.10-20.00					2.08	88.2	4343.0	
MA	EXTRUSION	0.08	6.00				1.47	12.9			
MA	EXTRUSION	0.08	1.00				12.0				
RA	PLATE	0.08	1.00				0.66	12.8			
RA	FORGING	0.08	1.00				5.54				

TABLE 4.11.1.7
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: S.T.M.
AT R.T.

CONDITION/MT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
BA	PLATE	0.10	1.00		11.1 163
DBTC	PLATE	0.08	1.00		0.62 13.9
MA	SHEET	0.08	1.00		3.22
MA	PLATE	0.03	1.00	SPEC THK=0.50"	87.5
MA	PLATE	0.03	1.00	SPEC THK=1.00"	589 31.3
MA	EXTRUSION	0.08	1.00		14.3 266.
MA	EXTRUSION	0.10	1.00-10.00		11.2 254.
RA	PLATE	0.08	0.10		11.0
RA	PLATE	0.08	1.00		0.59 8.98 344
RA	PLATE	0.08	1.00		9.34
RA	PLATE	0.08	1.00		0.77 13.4
RA	PLATE	0.30	1.00		2.27 24.5
RA	PLATE	0.50	1.00		4.23
RA	FORGING	0.08	1.00		1.65 36.8

TABLE 4.11.1.8

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN

ORIENTATION T-S

ENVIRONMENT: 3.5% NaCl
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)						
					2.5	5	10	20	50	100	
BA	PLATE	0.10	10.00		0.62	17.6					
RA	PLATE	0.10	10.00							49.7	

TABLE 4.11.1.9
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT DRY AIR AT RT

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
RA	PLATE	0.10	0.10	2.5	50
RA	PLATE	0.10	1.00	2.5	20
RA	PLATE	0.50	0.10	2.5	10
RA	PLATE	0.50	1.00	2.5	5
					224
					9.08
					20.4
					17.2

TABLE 4.11.1.10

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN
ORIENTATION T-LENVIRONMENT: L.H.A.
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	2.5	5	10	20	50	100
DB	PLATE	0.08	6.00				0.39	12.1		
DB	PLATE	0.30	6.00					33.1		
DBTC	PLATE	0.08	1.00						7.70	169
DBTC	PLATE	0.30	1.00						0.56	12.9 278
MA	SHEET	0.08	6.00							9.22
MA	PLATE	0.30	1.00-6.00						0.46	11.2 259
MA	EXTRUSION	0.08	6.00							12.7
RA	PLATE	0.08	6.00						0.53	11.4 208
RA	PLATE	0.08	6.00							9.89
RA	FORGING	0.08	6.00							7.65 135
RA	FORGING	0.30	6.00						2.68	19.8

TABLE 4.11.1.11
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN ORIENTATION: T-L

ENVIRONMENT: LAB AIR AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
AS WELDED E B WELDMENT (WELD ZONE)	WELDMENT	0.10	10.00	2.5 5 10 20 50 100	5.94
AS WELDED E. B. WELDMENT (HEAT AFFECTED ZONE)	WELDMENT	0.10	10.00		6.52
BA	FORGING	0.02	0 10-20.00		2.27 103 3242
MA	EXTRUSION	0.10	5 00-20.00		13.7 261.
RA	PLATE	0.10	10.00		21.3
STRESS RELIEVED E. B. WELDMENT (HEAT AFFECTED ZONE)	WELDMENT	0.10	0 10-10.00		14.2 344
STRESS RELIEVED E. B. WELDMENT (WELD ZONE)	WELDMENT	0.10	0 10-10.00		10.1

TABLE 4.11.1.12
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM TI-6AL-4V

TEST CONDITIONS		ENVIRONMENT: AIR AT 175 F		FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)							
SPECIMEN ORIENTATION	T-L	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
MA		PLATE	0.10	0	10-10.00				11.7	135	
STRESS RELIEVED E B WELDMENT (HEAT AFFECTED ZONE)		WELDMENT	0.10	0	10-10.00				8.82	150	

TABLE 4.11.1.13

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: H.H.A.
AT R.T.

CONDITION/HT	PRODUCT FURN	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
RA	PLATE	0.10	10.00					14.4			
RA	PLATE	0.10	10.00				3.97	23.8			
RA	PLATE	0.90	10.00		0.32	3.63	64.9				
RA	PLATE	0.50	10.00	DATA OUT OF TREND		6.45	26.8				

TABLE 4.11.1.14

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN
ORIENTATION T-LENVIRONMENT: JP-4 FUEL
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
BA	FORGING	0.02	0.10-20.00		2.40 103
RA	PLATE	0.08	1.00		0.72 14.2
STRESS RELIEVED F B WELDMENT (HEAT AFFECTED ZONE)	WELDMENT	0.10	0.10-10.00		9.65 1560

TABLE 4.11.1.15

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN
ORIENTATION T-LENVIRONMENT: WATER SATURATED JP-4 FUEL
AT R. T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
RA	PLATE	0.10	0.10		204
RA	PLATE	0.10	1.00		179
RA	PLATE	0.50	0.10		17.0
RA	PLATE	0.50	1.00		1.93 18.4

TABLE 4.11.1.16
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM 11-6AL-4V

TEST CONDITIONS		ENVIRONMENT	DIST. WATER AT R. T.	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE)								
SPECIMEN ORIENTATION	T-L			PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50
BA			PLATE	0.10	0.10							126
RA			PLATE	0.00	15.00			0.43				
RA			PLATE	0.10	0.10				19.0		254	
RA			PLATE	0.10	1.00						197	
RA			PLATE	0.50	0.10					21.8		
RA			PLATE	0.50	1.00				2.64	36.8		
STRESS RELIEVED E B WELDMENT (WELD ZONE)			WELDMENT	0.10	0.10-10.00							2052

TABLE 4.11.1.17

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: DIST. WATER AT 175 F

CONDITION/RT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
	PLATE	0.50	1.00	2.5 5 10 20 50 100	

RA					29.6

STRESS RELIEVED E B WELDMENT (HEAT AFFECTED ZONE)	WELDMENT	0.10	0 10-10 00		952

TABLE 4.11.1.18
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM T1-6AL-4V

TEST CONDITIONS		ENVIRONMENT		FATIGUE CRACK GROWTH RATES						
SPECIMEN ORIENTATION	T-L	3 SZINACL	AT R.T.	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100
(CONDITION/MT)	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)							
BA	PLATE	0.10	1.00				38.5	281		
BA	PLATE	0.10	10.00		0.98	13.8	109			
RA	PLATE	0.10	15.00		0.64					
RA	PLATE	0.10	0.10				1852			
RA	PLATE	0.10	0.10		3.50	44.7				
RA	PLATE	0.10	1.00		28.6	526				
RA	PLATE	0.10	10.00		4.86	63.0				
RA	PLATE	0.10	10.00			58.9				
RA	PLATE	0.50	0.10		2.95					
RA	PLATE	0.50	1.00		2.65	117				
RA	PLATE	0.50	10.00		33.7	168				
STRESS RELIEVED E B WELDMENT (WELD ZONE)									18134	
STRESS RELIEVED E B WELDMENT (HEAT AFFECTED ZONE)										13.9

TABLE 4.11.1.19
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM TI-6AL-4V

TEST CONDITIONS		ENVIRONMENT		S. T. W.		AT R. T.				
SPECIMEN ORIENTATION	T-L									
CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100
				DATA OUT OF TREND						
BA	PLATE	0.10	0.10				0.58	6.43	400	
BA	PLATE	0.10	1.00					35.3	192	
BA	PLATE	0.10	10.00					18.6	94.3	

DB	PLATE	0.08	1.00					8.20	214	

DB + 2DBTC	PLATE	0.08	1.00					7.93	244	

DB + 4DBTC	PLATE	0.08	1.00					9.03	209	

DBT + PC	PLATE	0.08	1.00					11.2		

DBTC	PLATE	0.08	1.00					1.83	18.4	

MA	EXTRUSION	0.08	6.00					0.62	11.1	
MA	EXTRUSION	0.10	1.00-10.00					25.9	324	

RA	PLATE	0.00	15.00					0.64		
RA	PLATE	0.08	1.00	DATA OUT OF TREND				2.08	48.7	
RA	PLATE	0.08	1.00					0.96	12.7	285

TABLE 4.11.1.19 (Con't)

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM 11-6AL-4V

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT S T M
A T R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2	5	10	20	50	100
RA	PLATE	0.08	1.00						9.12	
RA	PLATE	0.08	1.00						8.98	
RA	PLATE	0.10	0.10							905
RA	PLATE	0.10	0.10							3950
RA	PLATE	0.10	1.00							310
RA	PLATE	0.50	1.00			2.02	52.5			
RA	FORGING	0.08	1.00				16.1	225.		
RA	FORGING	0.08	1.00			0.69	14.0	192.		
RA	FORGING	0.08	1.00			0.74	14.9			
RA	FORGING	0.50	1.00			3.39	61.3			

TABLE 4.11.1.20

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN
ORIENTATION 5-TENVIRONMENT: S.T.M.
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
DB	PLATE	0.08	1 00		0.78 21.3
DB + TR	PLATE	0.08	1 00		9.78

TABLE 4.11.1.21

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONSSPECIMEN
ORIENTATION 1-RENVIRONMENT: AIR
AT 300 F

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
					FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
HA 1300F 2HRS AC	DISK	0.60	0.33							6.72
HA 1300F 2HRS AC	DISK	0.25	0.33							13.5
HA 1300F 2HRS AC	DISK	0.54	0.33							1.19

TABLE 4.11.1.22

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS		ENVIRONMENT		FATIGUE CRACK GROWTH RATES									
SPECIMEN ORIENTATION	R-C	ARGON	AT R. T.	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
1550F 4HRS FC. 1000F 4HRS. ARGON COOLED				FORGING	0.10	10.00				0.19	3.81		
1550F 4HRS FC. 1000F 4HRS. ARGON COOLED				FORGING	0.10	10.00					4.08		
1750F 4HRS ARGON COOLED, 1000F 4HRS, ARGON COOLED				FORGING	0.10	9.99					4.13		
1750F 4HRS ARGON COOLED, 1000F 4HRS, ARGON COOLED				FORGING	0.10	10.00					4.05		
1950F 4HRS WQ. 1000F 4HRS ARGON COOLED				FORGING	0.10	10.00					2.38	257	

TABLE 4.11.1.23

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN
ORIENTATION C-RENVIRONMENT: ARGON
AT R. T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
1750F 4HRS ARGON COOLED, 1000F 4HRS ARGON COOLED	FORGING	0.10	10.00	2.5 5 10 20 50 100	4.61
1950F 4HRS WQ, 1000F 4HRS ARGON COOLED	FORGING	0.10	10.00		3.37

TABLE 4.11.1.24

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN
ORIENTATION C-RENVIRONMENT: LAB AIR
AT R.T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
1775F 1HR WQ. 1675F 1HR WQ. 1000F 4HRS AC. 900F 3HR	DISK	0.05	0.33-10.00	2.5 5 10 20 50 100	152
1775F 1HR WQ. 1675F 1HR WQ. 1000F-1200F 2-8HRS AC	DISK	0.03	0.33- .90		0.86 11.0
1775F 1HR WQ. 1675F 1HR WQ. 1000F-1200F 2-8HRS AC	DISK	0.25	0.33- 50		18.9

TABLE 4.11.1.25

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V

TEST CONDITIONS

SPECIMEN
ORIENTATION C-RENVIRONMENT: AIR
AT 300 F

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
1775F 1HR WQ. 1675F 1HR WQ. 1000F-1200F 2-8HRS AC	DISK	0.03	0.33		0.74 10.1
1775F 1HR WQ. 1675F 1HR WQ. 1000F-1200F 2-8HRS AC	DISK	0.25	0.33		11.9

TABLE 4.11.1.26
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM TI-6AL-4V

TEST CONDITIONS		ENVIRONMENT	AIR	AT	600 F	FATIGUE CRACK GROWTH RATES							
SPECIMEN ORIENTATION	C-R					PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20
1775F 1HR WQ.						DISK	0.03	0.33			1.03	9.87	
1675F 1HR WQ.													
1000F-1200F	2-BARS AC												
1775F 1HR WQ.						DISK	0.03	0.33			1.77	12.6	
1675F 1HR WQ.													
1000F-1200F	2-BARS AC												
1775F 1HR WQ.						DISK	0.25	0.33			2.04	13.3	
1675F 1HR WQ.													
1000F-1200F	2-BARS AC												
1775F 1HR WQ.						DISK	0.54	0.33			2.12		
1675F 1HR WQ.													
1000F-1200F	2-BARS AC												

TABLE 4.11.2.1

CONDITION	--PRODUCT--		TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	TITANIUM		TI-6AL-4V		K(1C)	CRACK LENGTH (IN)	2.9σ K(1C)/TYB)±2 (IN)	K(1C) MEAN (KSI±SQRT IN)	STAN DEV	DATE	REFER
	FIRM	THICK (IN)				WIDTH (IN)	TRICK DESIGN	M	B							
AB FORGED-FA ALPHA-BETA FORGED, HILL ANNEALED	F	---	R.T.	---	133.0	2.500	1.250	CT	1.250	0.57	63.60	1973 90584	(1)			
		---			133.0	2.500	1.250	CT	1.250	0.50	59.40	1973 90584	(1)			
		---			134.0	2.500	1.250	CT	1.250	0.62	66.50	1973 90584	(1)			
		---			134.0	2.500	1.250	CT	1.250	0.41	54.10	1973 90584	(1)			
		---			134.0	2.500	1.250	CT	1.250	0.43	55.90	1973 90584	(1)			
4 HR. FC TO 1000F, AC		2.75			136.0	2.000	1.000	CT	1.000	0.44	56.30	1973 90584	(1)			
		2.75			136.0	2.000	1.000	CT	1.000	0.41	55.20	1974 88962 (2)	1974 88962 (2)			
AB FORGED-FA ALPHA-BETA FORGED, HILL ANNEALED	F	2.25	R.T.	T-L	145.0	2.000	1.000	CT	1.065	0.18	38.60	1973 86688	(1)			
		2.25			145.0	2.000	1.500	CT	1.556	0.12	32.20	1973 86688	(1)			
		2.25			145.0	2.000	1.000	CT	1.071	0.15	36.00	1973 86688	(1)			
		2.25			145.0	2.000	1.000	CT	1.074	0.14	34.90	1973 86688	(1)			
		---			---	---	---	---	---	---	---	---	---			
AB FORGED-FA ALPHA-BETA FORGED, RECRYSTALLIZED ANNEAL, 1700F 4 HR. FC TO 1000F, AC	F	---	R.T.	---	128.0	2.500	1.250	CT	1.250	0.74	67.90	1973 90584	(1)			
		---			128.0	2.500	1.250	CT	1.250	0.79	72.10	1973 90584	(1)			
		---			128.0	2.500	1.250	CT	1.250	0.72	68.60	1973 90584	(1)			
		---			128.0	2.500	1.250	CT	1.250	0.70	68.00	1973 90584	(1)			
		---			128.0	2.500	1.250	CT	1.250	0.74	69.60	1973 90534	(1)			
4 HR. FC TO 1000F, AC		---			128.0	2.500	1.250	CT	1.250	0.70	67.70	1973 90584	(1)			
		---			132.0	2.500	1.250	CT	1.250	0.60	64.50	1973 90584	(1)			
	---			132.0	2.500	1.250	CT	1.250	0.54	61.70	1973 90584	(1)				
ANNEALED	F	3.00	R.T.	L-T	114.0	3.001	1.501	CT	1.366	1.41	83.70	1973 85034	(1)			
		3.00			119.0	2.978	1.500	CT	1.556	1.22	83.10	1973 85034	(1)			
ANNEALED	F	3.00	R.T.	T-L	118.0	3.003	1.500	CT	1.549	1.46	90.40	1973 85034	(1)			
		3.00			120.0	3.001	1.494	CT	1.618	1.01	76.40	1973 85034	(1)			
ANNEALED	E	4.00	R.T.	L-T	122.0	4.006	1.624	CT	2.027	1.42	92.00	1973 85836	(3)			
ANNEALED	E	4.00	R.T.	T-L	122.0	4.003	1.639	CT	2.027	1.51	94.90	1973 85836	(3)			
		4.00			122.0	4.003	1.633	CT	1.995	1.41	91.70	1973 85836	(3)			
ANNEALED	BT	6.00	R.T.	L-T	123.0	2.501	1.250	CT	1.249	0.87	72.00	1975 MA003	(1)			

NOTES:
 (1) F-14 OUTBOARD COVER
 (2) CURF DISK
 (3) COMPOSITION (Wt PERCENT) 6.35AL, 4.31V, 0.022C, 0.16FE, 0.009N, 0.006H, 0.16O

TABLE 4.11.2.1 (con't)

CONDITION	--PRIDICK-- FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	TI-6AL-4V		CRACK LENGTH (IN)	2.5* (K(IC)/TYS)**2 (IN)	K(IC) (KSI*SQRT IN)	K(IC) STAN MEAN DEV (IN)	DATE	REFER		
						M	B								
ANNEALED 1375F 3 HR, AC	P	2.75	R.T.	L-T	129.0	2.497	1.250	CT	1.224	0.48	56.57	1975	MA003		
		2.75			129.0	2.477	1.250	CT	1.200	0.62	64.30	60.4/	5.5	1975	MA003
ANNEALED 2000F 2 HR	F	1.00	R.T.	--	140.0	2.000	1.000	CT	1.000	0.50	62.80	1974	88962 (1)		
		1.00			140.0	2.000	1.000	CT	1.000	0.43	58.20	1974	88962 (1)		
		1.00			140.0	2.000	1.000	CT	1.000	0.39	55.20	1974	88962 (1)		
		1.00			140.0	2.000	1.000	CT	1.000	0.44	50.80	1974	88962 (1)		
		1.00			140.0	2.000	1.000	CT	1.000	0.35	52.40	1974	88962 (1)		
												57.5/	3.9		
AS RECEIVED	FR	---	R.T.	L-T	124.0	2.000	1.002	CT	1.020	0.61	61.10	1974	90012		
		3.50			126.0	2.006	1.000	CT	1.074	0.59	61.30	1974	90012		
		1.00			126.0	1.997	1.001	CT	1.019	0.62	62.50	1974	90012		
		3.50			129.0	1.976	1.002	CT	1.006	0.59	61.30	1974	90012		
		---			130.0	1.998	1.000	CT	1.029	0.48	56.60	1974	90012		
		---			130.0	2.000	1.000	CT	1.053	0.79	72.90	1974	90012		
		3.50			131.0	1.970	0.998	CT	1.036	0.53	60.10	1974	90012		
		1.50			134.0	2.000	0.563	CT	1.005	0.72	70.60	1974	90012		
		---			134.0	1.998	1.003	CT	1.013	0.32	47.70	1974	90012		
		1.50			136.0	1.998	1.003	CT	1.053	0.61	66.10	1974	90012		
		2.50			137.0	2.000	0.999	CT	1.032	0.20	38.40	1974	90012		
		2.60			137.0	2.001	1.000	CT	1.021	0.37	52.90	1974	90012		
		2.70			143.0	2.001	0.999	CT	1.022	0.24	42.60	1974	90012		
												49.70	57.1/	10.4	
AS RECEIVED	FB	3.50	R.T.	T-L	127.0	1.978	0.998	CT	1.064	0.68	66.40	1974	90012		
		---			128.0	1.970	0.732	CT	1.023	0.42	52.50	1974	90012		
		1.00			129.0	1.997	0.779	CT	1.018	0.66	66.50	1974	90012		
		1.50			130.0	1.990	0.502	CT	1.000	0.41	52.60	1974	90012		
		---			130.0	1.779	0.649	CT	0.998	0.43	54.00	1974	90012		
		2.00			131.0	1.990	1.003	CT	1.023	0.53	60.10	1974	90012		
		1.50			132.0	1.999	1.002	CT	1.055	0.16	33.80	1974	90012		
		---			133.0	2.000	1.002	CT	1.027	0.69	69.90	1974	90012		
		---			133.0	1.998	1.001	CT	1.024	0.50	59.40	1974	90012		
		3.50			133.0	1.970	1.005	CT	1.043	0.56	62.70	1974	90012		
	3.50			134.0	2.000	1.000	CT	1.028	0.58	64.50	1974	90012			

NOTES
(1) INTERMEDIATE GRAIN SIZE

TABLE 4.11.2.1 (con't)

CONDITION	TITANIUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT (F)	THICK (IN)	TEMP (F)	SPECIMEN		WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5% CRACK LENGTH (K(TC)/TYB)?? (IN)	K(1C) (KRIEGRORT IN)	K(1C) MEAN DEVIATION (IN)	DATE	REFER
	FORM	THICKNESS					M	B									
AS RECEIVED	FB	1.50	R.T.	T-L	1.996	0.560	CT	0.994	0.45	57.40	1974	90012					
					2.003	1.001	CT	1.023	0.46	57.80	1974	90012					
					2.001	1.002	CT	1.016	0.44	58.20	1974	90012					
					2.000	0.634	CT	1.010	0.37	53.50	1974	90012					
					1.998	1.003	CT	1.033	0.35	52.10	1974	90012					
					2.002	0.999	CT	1.014	0.14	32.80	1974	90012					
					2.002	1.001	CT	1.033	0.18	37.40	1974	90012					
					1.999	0.999	CT	1.048	0.36	53.70	1974	90012					
					1.993	1.001	CT	1.034	0.35	66.89	1974	90012					
					2.000	0.999	CT	1.028	0.17	40.10	54.9/ 10.8	1974	90012				
AS RECEIVED-AB (ALPHA-BETA FORGED)	FB	3.50	R.T.	L-F	2.000	1.000	CT	1.033	0.92	77.10	1974	90012					
AS RECEIVED-AB (ALPHA-BETA FORGED)	FR	3.50	R.T.	T-L	2.000	1.000	CT	1.023	0.95	80.90	1974	90012					
R FORGED BETA FORGED REHEATED TO 1750F DRAWN TO SIZE, ANNEALED 1300F	FR	2.25	R.T.	T-L	2.000	1.000	CT	1.046	0.30	46.80	1973	86688					
		2.25			3.000	1.500	CT	1.471	0.20	37.80	1973	86688					
		2.25			2.000	1.000	CT	1.038	0.28	45.60	1973	86688					
		2.25			2.000	1.000	CT	1.058	0.22	40.20	42.6/ 4.3	1973	86688				
R FORGED-MA BETA FORGED, MILL ANNEALED, 1300F 2 HR, AC	F	2.75	R.T.		2.000	1.000	CT	1.000	0.88	77.70	1974	88962 (1)					
		2.75			2.000	1.000	CT	1.000	0.77	72.90	1974	88962 (1)					
R FORGED-MA BETA FORGED, MILL ANNEALED 1300F 2 HR, AC	F	2.00	R.T.	L-T	2.000	1.000	CT	---	0.59	66.40	1971	80338					
		2.00			2.000	1.000	CT	---	0.77	76.00	1971	80338					
		2.00			2.000	1.000	CT	---	0.64	67.30	1971	80338					
R FORGED-MA BETA FORGED, MILL ANNEALED 1300F 2 HR, AC	F	2.00	R.T.	T-L	2.000	1.000	CT	---	0.73	70.60	1971	80338					

NOTES:
(1) COMP. DISK

TABLE 4.11.2.1 (con't)

CONDITION	TITANIUM		YIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN)	DESIGN LENGTH (IN)	CRACK LENGTH (IN)	2.5* K(1C)/TYS (IN)	K(1C) MEAN DEV (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER
	FORM	TI-6AL-4V									
D FORCED-MA BETA FORGED, MILL ANNEALED 1300F 2 HR, AC	F	2.00	131.0	1.000	CT	---	0.74	71.10		1971	80338
		2.00	131.0	1.000	CT	---	0.74	71.40	71.0/ 0.4	1971	80338
E FORCED-MA BETA FORGED, MILL ANNEALED 1300F 2 HR, AC	F	2.00	132.0	1.000	CT	---	0.74	72.10		1971	80338
		2.00	132.0	1.000	CT	---	0.82	73.70	73.9/ 2.5	1971	80338
DB, AB FIN-MA BETA BLOCKED, ALPHA-BETA FINISHED, MILL ANNEALED	F	---	132.0	1.250	CT	1.250	0.78	73.50		1973	90384 (1)
		---	132.0	1.250	CT	1.250	0.89	78.70		1973	90384 (1)
		---	134.0	1.250	CT	1.250	0.59	65.10		1973	90384 (1)
		---	134.0	1.250	CT	1.250	0.72	72.10	72.4/ 5.6	1973	90384 (1)
DB, AB FIN-MA BETA BLOCKED, ALPHA-BETA FINISHED, RECRYSTALLIZED ANNEAL 1700F 4 HR, FC TO 1000F, AC	F	---	135.0	1.250	CT	1.250	0.87	80.70		1973	90384 (1)
		---	135.0	1.250	CT	1.250	0.76	74.40		1973	90384 (1)
		---	137.0	1.250	CT	1.250	0.74	74.80		1973	90384 (1)
		---	137.0	1.250	CT	1.250	0.66	70.50	73.1/ 4.3	1973	90384 (1)
EB, AB FIN-30% BETA BLOCKED, ALPHA-BETA FINISHED, 30% REDUCTION, MILL ANNEALED, 1300F 2 HR, AC	F	2.50	127.0	1.000	CT	1.000	1.00	80.50		1974	88962
		2.50	127.0	1.000	CT	1.000	0.89	75.90	78.2/ 3.3	1974	88962
EB, AB FIN-10% BETA BLOCKED, ALPHA-BETA FINISHED, 10% REDUCTION, SOLUTION TREATED & OVERAGED, 1750F 1 HR, WQ, 1300F 2 HR, AC	F	2.50	136.0	1.000	CT	1.000	0.84	72.00		1974	88962
		2.50	136.0	1.000	CT	1.000	0.99	83.50		1974	88962
		2.50	136.0	1.000	CT	1.000	0.88	80.50	81.7/ 3.4	1974	88962

NOTES:
/ 1) F-14 OUTBOARD COVER

TABLE 4.11.2.1 (con't)

CONDITION	TITANIUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT (F)	THICK (IN)	THICKNESS (IN)	SPECIMEN DESIGN (IN)	CRACK LENGTH (IN)	2.5* (IN)	K(1C) (KSI*SQRT IN)	K(1C) MEAN DEV (KSI*SQRT IN)	DATE	REF
	TI-6AL-4V	K(1C)											
08.8B FINISHED, ALPHA-BETA FINISHED, 30% REDUCTION, SOLUTION TREATED & OVERAGED, 1750F 1 HR, 40, 1300F 2 HR, AC	F	2 50	137.0	R.T.	2.000	1.000	CT	1.000	0.81	78.00		1974	88962
		2 50	137.0		2.000	1.000	CT	1.000	0.60	67.40		1974	88962
		2 50	137.0		2.000	1.000	CT	1.000	0.72	73.80	73.1/	1974	88962
											5.3		
08.8B FIN-10HA, BETA BLOCKED, BETA FINISHED, 10% REDUCTION, MILL ANNEALED, 1300F 2 HR, AC	F	2 50	128.0	R.T.	2.000	1.000	CT	1.000	0.85	74.50		1974	88962
		2 50	128.0		2.000	1.000	CT	1.000	0.84	74.40		1974	88962
		2 50	128.0		2.000	1.000	CT	1.000	0.77	71.10	73.3/	1974	88962
											1.9		
08.8B FIN10SDA, BETA BLOCKED, BETA FINISHED, 10% REDUCTION, SOLUTION TREATED & OVERAGED, 1750F 1 HR, 40, 1300F 2 HR, AC	F	2 50	138.0	R.T.	2.000	1.000	CT	1.000	0.96	85.60		1974	88962
		2 50	138.0		2.000	1.000	CT	1.000	0.98	86.40		1974	88962
		2 50	138.0		2.000	1.000	CT	1.000	0.98	86.40	86.1/	1974	88962
											0.5		
BETA ANNEALED PLATE EB WELDED THEN BETA ANNEALED WELDED IN PLANE OF FRACTURE	P	2 50	116.0	R.T.	1.994	0.999	CT	1.133	0.90	67.80		1974	88575
		2 50	116.0		1.992	0.951	CT	1.140	0.87	68.50	69.2/	1974	88575
											0.9		
BETA ANNEALED	P	2 50	125.0	65	3.997	2.001	CT	2.072	1.90	109.10		1974	88575
		2 50	125.0		4.003	1.998	CT	2.105	1.79	105.90		1974	88575
		2 50	125.0		4.003	1.991	CT	2.116	2.06	113.50		1974	88575
		2 50	125.0		4.003	2.000	CT	2.192	1.95	110.50		1974	88575
		2 50	125.0		4.009	2.005	CT	2.084	1.86	108.00	109.4/	1974	88575
											2.8		
BETA ANNEALED	P	1 00	126.0	R.T.	2.500	1.000	WDL	----	0.98	79.20		1977	JEM01
BETA PROCESSED MILL ANNEALED	P	3 00	130.4	R.T.	3.000	1.500	CT	----	1.44	99.00		1975	UD008
		3 00	130.4		3.000	1.500	CT	----	1.35	96.00		1975	UD008
		3 00	130.4		3.000	1.500	CT	----	1.18	87.60	94.9/	1975	UD008
											4.8		

TABLE 4.11.2.1 (con't)

CONDITION	TITANIUM		YIELD (KSI)	STRENGTH (KSI)	SPECIMEN ORIENT	TEST TEMP (F)	FORM (IN)	THICK (IN)	TI-GAL-4V		K(1C)	CRACK LENGTH (IN)	K(1C) (KSI*SQRT IN)	K(1C) MEAN (KSI)	STAN DEV	DATE	REFER
	W	B							DESIGN	THICK							
DIFFUSION BONDED	P	0.62	R.T.	120.0	---	---	0.62	4.003	2.002	CT	1.966	1.47	92.10			1973	85836 (1)
DIFFUSION BONDED	P	0.62	R.T.	120.0	L-T	---	0.62	3.004	1.500	CT	1.974	1.11	79.90			1973	85836 (1)
DIFFUSION BONDED	P	0.62	R.T.	120.0	T-L	---	0.62	3.005	1.501	CT	1.975	1.20	83.10			1973	85836 (1)
DIFFUSION BONDED	P	1.50	R.T.	120.0	S-T	---	1.50	4.000	1.500	CT	---	1.34	88.00			1974	89004 (1)
		1.50		120.0			1.50	4.000	1.500	CT	---	1.31	87.00			1974	89004 (1)
		1.50		120.0			1.50	4.000	1.500	CT	---	1.16	82.00	89.7/	3.2	1974	89004 (1)
DIFFUSION BONDED	P	2.50	R.T.	120.0	S-L	---	2.50	4.000	1.500	CT	---	1.14	81.00			1974	89004 (1)
DIFFUSION BONDED	BT	0.62	R.T.	120.0	L-T	---	0.62	3.000	1.500	CT	---	1.11	80.00			1974	89004 (1)
DIFFUSION BONDED ANNEALED	BT	3.50	R.T.	127.0	L-T	---	3.50	2.000	1.000	CT	1.072	0.93	77.50			1974	90012 (2)
		1.00		129.0			1.00	2.001	1.002	CT	1.092	0.98	80.70			1974	90012 (2)
		---		129.0			---	2.002	1.004	CT	1.032	0.75	70.80			1974	90012 (2)
		1.50		132.0			1.50	2.000	1.003	CT	1.019	0.45	56.10			1974	90012 (2)
		---		132.0			---	1.995	1.000	CT	1.083	0.83	76.30			1974	90012 (2)
		3.50		132.0			3.50	1.999	1.003	CT	1.029	0.68	69.00			1974	90012 (2)
		2.60		133.0			2.60	1.996	0.975	CT	1.017	0.48	58.10			1974	90012 (2)
		3.70		134.0			3.70	1.999	1.000	CT	1.030	0.69	70.40			1974	90012 (2)
		2.70		137.0			2.70	2.000	1.001	CT	1.024	0.40	54.70	68.2/	9.7	1974	90012 (2)
DIFFUSION BONDED	BT	0.62	R.T.	120.0	T-L	---	0.62	3.000	1.500	CT	---	1.20	83.00			1974	87004 (1)
DIFFUSION BONDED ANNEALED	BT	---	R.T.	125.0	T-L	---	---	2.000	1.003	CT	1.032	0.80	70.80			1974	90012 (2)
		---		125.0			---	1.997	0.676	CT	0.992	0.65	64.00			1974	90012 (2)
		---		128.0			---	2.001	0.999	CT	1.043	0.90	76.90			1974	90012 (2)
		3.50		131.0			3.50	1.973	1.000	CT	1.048	0.84	76.00			1974	90012 (2)
		3.50		132.0			3.50	1.998	0.999	CT	1.013	0.67	60.20			1974	90012 (2)
		2.60		133.0			2.60	1.998	1.000	CT	1.028	0.75	72.70			1974	90012 (2)
		3.50		133.0			3.50	2.000	0.999	CT	1.019	0.72	71.40			1974	90012 (2)

NOTES:
 (1) DIFFUSION BONDED - 1700F 4HR, FC TO 1400F AT 100F/HR THEN TO 900F IN 0.75HR
 (2) DIFFUSION BONDED ANNEALED - 1750F 1.5 TO 4HR, FC TO 900F AT 100F/HR

TABLE 4.11.2.1 (con't)

CONDITION	TITANIUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	R. T.	THICK (IN)	FORM	SPECIMEN		DESIGN	CRACK LENGTH (IN)	K (IC) (IN)	2.5° K (IC)/TYS)*2 (IN)	K (IC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER	
	TI-6AL-4V							W	B									A
	WIDTH (IN)	THICK (IN)																
DIFFUSION DIBID ANNEALED	BT	1.50	134.0	Y-L		2.000	1.000	CT	1.043	0.39	53.10				1974	90012 (1)		
			135.0			2.000	1.001	CT	1.033	0.66	69.20				1974	90012 (1)		
		2.50	137.0			1.998	0.877	CT	1.021	0.33	47.50				1974	90012 (1)		
		2.60	138.0			1.997	0.979	CT	1.031	0.25	43.10				1974	90012 (1)		
		2.70	140.0			2.000	1.004	CT	1.018	0.27	44.60				1974	90012 (1)		
	1.00	142.0			2.001	1.000	CT	1.042	0.66	72.70				1974	90012 (1)	64.2/ 11.8		
DIFFUSION UNHEAT	BT	8.00	---	S-T		3.999	1.495	CT	1.926	1.32	87.40				1972	84306 (2)		
		8.00	---			3.999	1.497	CT	1.881	1.18	82.40				1972	84306 (2)		
		8.00	---			3.998	1.495	CT	1.920	1.33	87.80				1972	84306 (2)		
		8.00	---			3.998	1.495	CT	1.963	1.43	90.90				1972	84306 (2)		
		8.00	---			3.998	1.492	CT	1.969	1.45	91.60				1972	84306 (2)	88.0/ 3.6	
HA COARSE GRAIN 1300F 2 HR. AC	F	14.00	139.0	--		2.000	1.000	CT	1.000	0.35	52.20				1974	88962		
		14.00	139.0			2.000	1.000	CT	1.000	0.36	53.20				1974	88962		
		14.00	139.0			2.000	1.000	CT	1.000	0.40	53.30				1974	88962		
		14.00	139.0			2.000	1.000	CT	1.000	0.42	56.70				1974	88962		
		14.00	139.0			2.000	1.000	CT	1.000	0.35	52.10				1974	88962	53.9/ 2.0	
HA FINE GRAIN 1300F 2 HR. AC	F	6.00	138.0	---		2.000	1.000	CT	1.000	0.44	59.60				1974	88962		
		6.00	138.0			2.000	1.000	CT	1.000	0.62	64.10				1974	88962		
		6.00	138.0			2.000	1.000	CT	1.000	0.60	67.60				1974	88962		
		6.00	138.0			2.000	1.000	CT	1.000	0.54	64.00				1974	88962		
		6.00	138.0			2.000	1.000	CT	1.000	0.85	80.60				1974	88962		
	6.00	138.0			2.000	1.000	CT	1.000	0.76	76.10				1974	88962	67.3/ 7.7		
HA 10-20% TO 20% PRIMARY ALPHA. MILL ANNEALED 1300F 2 HR. AC	F	2.50	141.0	---		2.000	1.000	CT	1.000	0.57	67.10				1974	88962		
		2.50	141.0			2.000	1.000	CT	1.000	0.67	73.10				1974	88962		
		2.50	141.0			2.000	1.000	CT	1.000	0.58	68.00				1974	88962	69.4/ 3.2	

NOTES:
 (1) DIFFUSION AND ANNEALED = 1700F 1.5 TO 4HR. FC TO 900F AT 100F/HR
 (2) DIFFUSION BONDED = 1700F 4HR. FC TO 1400F AT 100F/HR THEN TO 900F IN 0.75HR

TABLE 4.11.2.1 (con't)

CONDITION:		TITANIUM		II-6AL-4V		K(IIC)		K(IIC)		K(IIC) STAN		DATE		REFER	
FORM	THICK (IN)	TEST SPECIMEN ORIENT (°)	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN LENGTH (IN)	CRACK LENGTH (IN)	2.3% (K(IIC)/TYS)**2 (IN)	2.3% (K(IIC)/TYS)**2 (IN)	MEAN (K(IIC) REPORT IN)	DEV (K(IIC) REPORT IN)				
				A	B										
MA 40-50ZALPHA	F	2.50	135.0	2.000	1.000	CT	1.000	0.70	0.70	71.50			1974	88962	
40 TO 50Z		2.50	135.0	2.000	1.000	CT	1.000	0.58	0.58	63.20			1974	88962	
PRIMARY ALPHA,		2.50	135.0	2.000	1.000	CT	1.000	0.68	0.68	70.60	69.17	3.4	1974	88962	
MILL ANNEALED 1370F 2 HR.AC															
MILL ANNEAL	P	1.50	133.0	2.496	1.244	CT	1.330	0.45	0.45	54.59			1981	MA002	
		1.50	133.0	2.502	1.255	CT	1.297	0.42	0.42	54.70	55.67	1.3	1981	MA002	
MILL ANNEAL	P	1.00	146.1	2.550	1.000	WDL	----	0.17	0.17	38.20			1977	JEM01	
MILL ANNEALED	P	2.00	127.0	4.000	2.003	CT	2.137	1.94	1.94	112.00			1972	85064	
MILL ANNEALED	P	2.00	157.0	4.000	2.002	CT	1.980	0.94	0.94	83.70			1973	88144	
		2.00	157.0	4.000	2.004	CT	1.970	1.03	1.03	89.70			1973	88144	
		2.00	157.0	4.000	2.003	CT	1.990	0.99	0.99	88.20	87.97	2.0	1973	88144	
MILL ANNEALED	P	1.25	119.4	3.475	1.245	CT	1.741	1.16	1.16	93.30			1972	84306	
		1.25	119.4	3.479	1.245	CT	1.824	1.20	1.20	97.00			1972	84306	
		1.25	119.4	3.500	1.247	CT	1.817	1.15	1.15	94.80			1972	84306	
		2.00	126.0	4.000	2.002	CT	2.038	1.53	1.53	98.70			1972	85064	
		2.00	126.0	4.000	2.001	CT	2.097	1.94	1.94	112.00			1972	85064	
		2.00	126.0	4.000	2.002	CT	2.048	1.75	1.75	103.90	100.67	6.8	1972	85064	
MILL ANNEALED	E	4.00	123.5	3.997	1.465	CT	1.937	1.21	1.21	87.60			1972	84306 (1)	
		1.80	124.0	3.934	1.578	CT	2.031	1.17	1.17	85.09			1976	MC001	
		1.80	124.0	3.930	1.578	CT	2.036	1.12	1.12	83.06			1976	MC001	
		1.80	124.5	3.995	1.577	CT	2.049	1.09	1.09	82.37			1976	MC001	
		1.80	124.5	3.995	1.578	CT	2.115	1.01	1.01	79.17	83.57	3.1	1976	MC001	
MILL ANNEALED	E	4.00	---	4.000	1.496	CT	1.947	1.30	1.30	92.50			1972	84306 (2)	
		1.80	125.5	3.995	1.575	CT	2.102	1.06	1.06	81.82			1976	MC001	
		1.80	125.5	3.995	1.577	CT	2.113	1.21	1.21	87.42			1976	MC001	
		1.80	127.0	3.995	1.578	CT	2.096	1.13	1.13	85.71			1976	MC001	
		1.80	127.0	3.738	1.577	CT	2.079	1.13	1.13	83.64	87.57	4.1	1976	MC001	

NOTES

- (1) COMPOSITION (WGT PERCENT) 6.51AL, 4.06V, 0.02AC, 0.19FE, 0.012N, 0.0064H, 0.150
(2) COMPOSITION (WGT PERCENT) 6.35AL, 4.31V, 0.022C, 0.14FE, 0.0079N, 0.0064H, 0.160

TABLE 4.11.2.1 (con't)

CONDITION	TITANIUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT (F)	THICK (IN)	FORM	SPECIMEN		CRACK LENGTH (IN)	2.5* CRACK LENGTH (K(IIC)/TYS)**2 (IN)	K(IIC) MEAN (KBI/ROOT IN)	STAN DEV	DATE	REFL	
	T1-6AL-4V	K(IIC)					WIDTH (IN)	THICK DESIGN (IN)							
MILL ANNEALED 1200F 2HR.AC	F	4.50	R.T.	L-T	130.0	2.478	1.248	CT	1.355	0.54	60.59		1981	MA002	
MILL ANNEALED 1300F 2 HR.AC	F	2.00	R.T.	L-T	132.0	2.000	1.000	CT	---	0.31	46.70		1971	80538	
MILL ANNEALED 1300F 2 HR.AC	F	2.00	R.T.	L-T	132.0	2.000	1.000	CT	---	0.30	45.40		1971	80538	
MILL ANNEALED 1300F 2 HR.AC	F	2.00	R.T.	L-T	133.0	2.000	1.000	CT	---	0.37	51.00	47.7/	2.9	1971	80538
MILL ANNEALED 1300F 2 HR.AC	F	2.00	R.T.	T-L	133.0	2.000	1.000	CT	---	0.30	46.50		1971	80538	
MILL ANNEALED 1300F 2 HR.AC	F	2.00	R.T.	S-L	133.0	2.000	1.000	CT	---	0.32	48.00		1971	80538	
MILL ANNEALED 1300F 2 HR.AC	F	2.00	R.T.	S-L	140.0	2.000	1.000	CT	---	0.41	53.90	49.5/	3.9	1971	80538
MILL ANNEALED 1300F 2 HR.AC	F	2.00	R.T.	S-L	140.0	2.000	1.000	CT	---	0.18	37.90		1971	80538	
MILL ANNEALED 1300F 2 HR.AC	F	2.00	R.T.	S-L	140.0	2.000	1.000	CT	---	0.31	49.50		1971	80538	
MILL ANNEALED 1300F 2 HR.AC	F	2.00	R.T.	S-L	140.0	2.000	1.000	CT	---	0.24	43.50	43.6/	5.8	1971	80538
MILL ANNEALED 1300F 2 HR.AC	BT	2.50	R.T.	L-T	120.0	2.500	1.250	CT	1.277	1.13	60.50		1971	84360	
MILL ANNEALED 1300F 2 HR.AC	BT	2.50	R.T.	L-T	127.0	2.500	1.250	CT	1.271	1.16	86.80		1971	84360	
MILL ANNEALED 1300F 2 HR.AC	BT	2.50	R.T.	L-T	127.0	2.498	1.251	CT	1.225	1.11	85.00	84.0/	3.4	1971	84360
RECRYSTALLIZE ANNEAL	P	1.50	-	65	L-T	---	3.999	1.502	CT	2.044	60.40		1972	84306 (1)	
RECRYSTALLIZE ANNEAL	F	1.50	R.T.	L-T	118.0	4.003	1.502	CT	2.021	0.97	74.90		1972	84306 (1)	
RECRYSTALLIZE ANNEAL	F	1.50	R.T.	L-T	118.0	4.005	1.502	CT	2.004	1.08	79.00		1972	84306 (1)	
RECRYSTALLIZE ANNEAL	F	2.00	R.T.	L-T	119.0	6.003	1.873	CT	3.138	1.43	96.40		1972	84306 (1)	
RECRYSTALLIZE ANNEAL	F	2.00	R.T.	L-T	119.0	6.002	1.780	CT	3.075	1.64	97.50		1972	84306 (1)	
RECRYSTALLIZE ANNEAL	F	1.50	R.T.	L-T	120.0	4.000	1.501	CT	2.103	1.16	81.80		1973	85836 (1)	
RECRYSTALLIZE ANNEAL	F	2.50	R.T.	L-T	120.0	4.000	2.000	CT	---	0.95	74.00		1974	89004 (1)	
RECRYSTALLIZE ANNEAL	F	2.50	R.T.	L-T	120.0	4.000	2.000	CT	---	1.11	80.00		1974	89004 (1)	
RECRYSTALLIZE ANNEAL	F	1.25	R.T.	L-T	120.0	---	1.250	CT	---	1.08	79.00		1974	89004 (1)	
RECRYSTALLIZE ANNEAL	F	2.50	R.T.	L-T	120.0	2.979	1.126	CT	1.926	0.83	67.00		1973	85836 (1)	
RECRYSTALLIZE ANNEAL	F	1.25	R.T.	L-T	120.0	---	1.250	CT	---	1.03	77.00		1974	89004 (1)	
RECRYSTALLIZE ANNEAL	F	2.50	R.T.	L-T	120.0	---	1.250	CT	---	1.38	87.00		1974	89004 (1)	
RECRYSTALLIZE ANNEAL	F	1.25	R.T.	L-T	120.0	---	1.250	CT	---	0.98	75.00		1974	89004 (1)	
RECRYSTALLIZE ANNEAL	F	2.50	R.T.	L-T	120.0	---	1.250	CT	---	1.31	87.00		1974	89004 (1)	
RECRYSTALLIZE ANNEAL	F	1.25	R.T.	L-T	120.0	---	1.250	CT	---	0.92	73.00		1974	89004 (1)	
RECRYSTALLIZE ANNEAL	F	2.50	R.T.	L-T	120.0	4.000	2.000	CT	---	1.17	82.00		1974	89004 (1)	

NOTES
1. 1) RECRYSTALLIZE ANNEAL=1700F 4 HR. FC TO 1400F AT 100F/HR. COOL TO 900F IN 1.75HR

TABLE 4.11.2.1 (con't)

CONDITION	TI-6AL-4V		K(1C)	SPECIMEN		YIELD STRENGTH (KSI)	ORIENT	TEST TEMP (F)	WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.9% K(1C)/TYS**2 (IN)	K(1C) MEAN (K(1C) REPORT IN)	STAN DEV	DATE	REFER
	FINN	PRODUCT		M	B												
RECRYSTALLIZE ANNEAL	P	1.25	R.T.	L-T	120.0	---	1.250	CT	---	---	---	1.14	81.00	---	---	1974	89004 (1)
		1.50			120.0	6.000	1.370	CT	---	---	---	1.11	80.00	---	---	1974	89004 (1)
		1.50			121.0	6.000	1.476	CT	3.080	---	---	1.44	91.00	---	---	1972	84306 (1)
		1.50			121.0	3.500	1.500	CT	---	---	---	1.29	87.00	---	---	1974	89004 (1)
		1.50			121.0	3.500	1.500	CT	---	---	---	1.44	92.00	---	---	1974	89004 (1)
		1.50			121.0	6.000	1.500	CT	3.103	---	---	1.30	86.60	---	---	1972	84306 (1)
	1.50			121.0	6.001	1.497	CT	3.065	---	---	1.41	90.20	---	---	1972	84306 (1)	
													82.8/	7.8			
RECRYSTALLIZE ANNEAL	P	1.50	65	T-L	---	3.997	1.476	CT	2.110	---	---	1.03	77.00	---	---	1972	84306 (1)
RECRYSTALLIZE ANNEAL	P	2.50	R.T.	T-L	120.0	3.000	1.108	CT	---	---	---	0.83	69.30	---	---	1973	85836 (1)
		2.50			120.0	---	1.250	CT	1.520	---	---	0.92	73.00	---	---	1974	89004 (1)
		2.50			120.0	4.000	2.000	CT	---	---	---	1.25	85.00	---	---	1974	89004 (1)
		2.50			120.0	---	1.250	CT	---	---	---	1.00	76.00	---	---	1974	89004 (1)
		2.50			120.0	4.000	2.000	CT	---	---	---	0.83	69.00	---	---	1974	89004 (1)
		2.50			120.0	---	---	---	CT	---	---	1.50	93.00	---	---	1974	89004 (1)
		2.00			120.0	6.001	2.009	CT	3.048	---	---	1.97	106.40	---	---	1973	85836 (1)
		1.25			120.0	---	1.250	CT	---	---	---	0.95	74.00	---	---	1974	89004 (1)
		1.50			120.0	6.000	1.370	CT	---	---	---	1.28	86.00	---	---	1974	89004 (1)
		1.50			120.0	4.001	1.478	CT	2.131	---	---	1.45	91.50	---	---	1973	85836 (1)
		1.25			120.0	---	1.250	CT	---	---	---	1.14	81.00	---	---	1974	89004 (1)
		2.50			120.0	4.000	2.000	CT	---	---	---	0.98	75.00	---	---	1974	89004 (1)
	2.50			120.0	3.000	1.500	CT	---	---	---	1.25	85.00	---	---	1974	89004 (1)	
	2.50			120.0	---	---	---	CT	---	---	1.44	91.00	---	---	1974	89004 (1)	
	2.50			120.0	3.000	1.127	CT	1.344	---	---	0.90	71.90	---	---	1973	85836 (1)	
	2.00			120.0	5.999	1.997	CT	3.056	---	---	1.79	101.50	---	---	1973	85836 (1)	
	2.50			120.0	2.997	1.374	CT	1.534	---	---	0.84	69.40	---	---	1973	85836 (1)	
	2.50			120.0	---	---	---	CT	---	---	1.14	81.00	---	---	1974	89004 (1)	
	1.25			120.0	---	---	---	CT	---	---	0.85	70.00	---	---	1974	89004 (1)	
	2.50			120.0	4.000	2.000	CT	---	---	---	1.00	76.00	---	---	1974	89004 (1)	
	1.50			121.0	3.500	1.500	CT	---	---	---	1.18	83.00	---	---	1974	89004 (1)	
	1.00			135.0	2.550	1.000	WOL	---	---	---	0.65	69.20	---	---	1977	JEM01 (2)	
RECRYSTALLIZE ANNEAL	F	---	R.T.	L-T	---	3.000	1.500	CT	---	---	---	1.03	77.00	---	---	1974	89004 (2)
		---			---	4.000	2.030	CT	---	---	---	1.20	83.00	---	---	1974	89004 (2)
		---			---	3.000	1.500	CT	---	---	---	0.92	73.00	---	---	1974	89004 (2)
		2.25			114.0	2.977	1.499	CT	1.528	---	---	1.06	78.00	---	---	1974	89004 (2)
													86.10	---	---	1973	85034 (1)

NOTES

(1) RECRYSTALLIZE ANNEAL=1700F 4 HR. FC TO 1400F AT 100F/HR. COOL TO 900F IN 75HR

(2) RECRYSTALLIZE ANNEAL=1700F 4 HR. FC TO 1400F AT 100F/HR. COOL TO 900F IN 75HR

TYS: APPNDX 120

TABLE 4.11.2.1 (con't)

CONDITION	RECRYSTALLIZE	FORM	THICK (IN)	TEMP (F)	ORIENT	YIELD STRENGTH (KSI)	TITANIUM		K(1C)	CRACK LENGTH (IN)	2.5% K(1C)/TYS)**2 (IN)	K(1C) MEAN (KBI-GMOT IN)	STAN DEV	DATE	REFER
							WIDTH (IN)	THICK (IN)							
	F	2.25	R.T.	1-1		115.0	2.999	1.500	CT	1.524	1.49	89.00		1973	85034 (1)
RECRYSTALLIZE	F	2.25	R.T.	1-1		116.0	2.978	1.499	CT	1.939	1.50	83.60		1973	85034 (1)
ANNEAL		3.40				117.0	2.979	1.503	CT	1.934	1.47	89.70		1973	85034 (1)
		2.25				117.0	3.002	1.500	CT	1.539	1.05	76.00		1973	85034 (1)
		5.62				118.0	3.004	1.499	CT	1.940	1.46	90.30		1973	85034 (1)
		3.25				118.0	2.999	1.499	CT	1.526	1.19	81.30		1973	85034 (1)
		5.62				119.0	3.008	1.497	CT	1.536	1.46	90.90		1973	85034 (1)
		2.20				119.0	3.007	1.498	CT	1.563	1.49	91.90		1973	85857 (1)
		3.20				119.0	3.003	1.500	CT	1.952	1.36	87.60		1973	85857 (1)
		3.40				119.0	3.002	1.501	CT	1.933	1.39	80.90		1973	85034 (1)
		2.20				120.0	3.006	1.502	CT	1.981	1.41	90.10		1973	85857 (1)
		6.70				121.0	3.000	1.502	CT	1.941	0.96	75.10		1973	85034 (1)
		1.20				121.0	3.004	1.376	CT	1.615	1.23	84.40		1973	85857 (1)
		1.20				121.0	3.005	1.374	CT	1.989	1.27	86.10		1973	85857 (1)
		1.20				121.0	3.010	1.345	CT	1.956	1.15	82.10		1973	85857 (1)
		6.70				121.0	3.001	1.500	CT	1.948	1.04	78.70		1973	85034 (1)
		2.20				121.0	3.003	1.502	CT	1.989	1.17	82.60		1973	85857 (1)
		2.20				122.0	3.003	1.499	CT	1.633	1.24	85.10		1973	85857 (1)
		2.20				122.0	3.009	1.318	CT	1.983	1.12	83.90		1973	85857 (1)
		1.20				123.0	2.998	1.417	CT	1.993	0.95	81.70		1973	85034 (1)
		1.20				123.0	3.006	1.377	CT	1.605	1.17	75.90		1973	85857 (1)
		1.20				123.0	3.002	1.377	CT	1.978	0.80	84.30		1973	85034 (1)
		2.20				124.0	3.003	1.501	CT	1.607	1.16	73.20		1973	85857 (1)
		1.20				124.0	3.004	1.409	CT	1.977	0.94	84.40		1973	85034 (1)
		3.20				124.0	3.001	1.504	CT	1.983	1.49	93.70		1973	85857 (1)
		1.20				124.0	2.999	1.504	CT	1.985	0.98	77.60		1973	85034 (1)
		2.20				124.0	3.005	1.504	CT	1.949	1.08	81.50		1973	85034 (1)
		1.20				125.0	3.001	1.375	CT	1.612	1.14	81.60		1973	85857 (1)
		2.20				126.0	3.003	1.495	CT	1.991	1.11	83.60		1973	85857 (1)
		1.20				127.0	3.001	1.248	CT	1.542	1.17	86.70		1973	85857 (1)
		1.20				127.0	3.003	1.250	CT	1.527	1.24	89.50		1973	85857 (1)
		1.20				127.0	3.001	1.250	CT	1.983	1.20	88.00		1973	85857 (1)
		1.20				129.0	2.979	1.248	CT	1.988	1.07	84.40		1973	85857 (1)
		1.20				129.0	2.997	1.249	CT	1.440	1.08	84.60		1973	85857 (1)
		1.20				130.0	3.002	1.372	CT	1.560	0.92	78.80		1973	85034 (1)
RECRYSTALLIZE	F	---	R.T.	1-1		---	3.500	1.750	CT	---	1.31	87.00		1974	89004 (2)
ANNEAL															

83.6/ 9.5

NOTES:
 (1) RECRYSTALLIZE ANNEAL=1700F 4 HR, FC TO 1400F AT 100F/HR, COOL TO 900F IN .75HR
 (2) RECRYSTALLIZE ANNEAL=1700F 4 HR, FC TO 1400F AT 100F/HR, COOL TO 900F IN .75HR
 TYS: APPRIK 120

TABLE 4.11.2.1 (con't)

CONDITION	TITANIUM		YIELD STRENGTH (KSI)	TEST TEMP (F)	R.T.	T-L	SPECIMEN		CRACK LENGTH (IN)	2.5* K(1C)/TVS**2 (IN)	K(1C) MEAN DEV (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER
	TI-6AL-4V	K(1C)					WIDTH (IN)	THICK (IN)						
RECRYSTALLIZE	F	---	---	---	---	---	3.000	1.500	CT	---	77.00		1974	89004 (1)
ANNEAL	F	---	---	---	---	---	3.000	1.500	CT	---	70.00		1974	89004 (1)
		---	---	---	---	---	3.500	1.750	CT	---	90.00		1974	89004 (1)
		3.40	116.0				3.000	1.502	CT	1.544	85.70		1973	85034 (1)
		5.62	117.0				3.001	1.500	CT	1.537	82.50		1973	85034 (1)
		6.70	118.0				2.997	1.501	CT	1.578	85.80		1973	85034 (1)
		5.62	119.0				3.001	1.500	CT	1.543	81.80		1973	85034 (1)
		3.40	119.0				3.002	1.500	CT	1.545	84.90		1973	85034 (1)
		5.62	120.0				2.977	1.499	CT	1.518	77.00		1973	85034 (1)
		3.50	120.0				3.007	1.502	CT	1.574	88.40		1973	85857 (1)
		5.62	120.0				3.005	1.498	CT	1.520	84.70		1973	85034 (1)
		1.90	121.0				3.004	1.500	CT	1.573	80.20		1973	85857 (1)
		6.70	121.0				3.002	1.500	CT	1.546	68.80		1973	85034 (1)
		1.90	122.0				3.000	1.245	CT	1.475	84.80		1973	85857 (1)
		1.90	122.0				3.000	1.248	CT	1.547	75.50		1973	85857 (1)
		3.40	123.0				2.998	1.497	CT	1.493	70.40		1973	85034 (1)
		4.75	123.0				3.004	1.502	CT	1.558	82.00		1973	85034 (1)
		6.70	123.0				3.000	1.501	CT	1.544	89.60		1973	85034 (1)
		3.50	123.0				2.978	1.500	CT	1.530	87.20		1973	85034 (1)
		2.20	124.0				3.002	1.502	CT	1.572	87.30		1973	85857 (1)
		6.70	124.0				2.996	1.502	CT	1.501	83.00		1973	85034 (1)
		4.75	125.0				3.001	1.502	CT	1.541	87.90		1973	85034 (1)
		2.20	125.0				3.006	1.498	CT	1.593	90.30		1973	85857 (1)
		3.20	126.0				3.000	1.508	CT	1.589	90.70		1973	85857 (1)
		2.25	126.0				2.993	1.502	CT	1.535	91.50		1973	85034 (1)
		3.20	126.0				2.998	1.500	CT	1.516	90.50		1973	85034 (1)
		2.20	126.0				3.000	1.501	CT	1.521	96.50		1973	85857 (1)
		2.25	127.0				3.008	1.502	CT	1.733	94.40		1973	85857 (1)
		2.20	127.0				3.001	1.500	CT	1.532	93.10		1973	85034 (1)
		2.20	127.0				3.002	1.500	CT	1.577	81.40		1973	85857 (1)
		1.90	128.0				3.002	1.500	CT	1.595	79.70		1973	85034 (1)
		3.20	128.0				3.006	1.500	CT	1.601	75.90		1973	85857 (1)
		1.50	129.0				3.001	1.377	CT	1.575	73.40		1973	85034 (1)
		1.50	129.0				3.003	1.424	CT	1.583	74.20		1973	85034 (1)
		1.50	129.0				2.979	1.355	CT	1.586	82.90		1973	85034 (1)
		1.50	129.0				3.000	1.367	CT	1.586	82.20		1973	85034 (1)
		1.20	130.0				3.004	1.347	CT	1.587	92.50		1973	85857 (1)
		1.50	130.0				3.001	1.368	CT	1.564	88.60		1973	85034 (1)
		1.20	130.0				3.010	1.319	CT	1.649	90.80		1973	85857 (1)

NOTES: (1) RECRYSTALLIZE ANNEAL=1700F 4 HR. FC TO 1400F AT 100F/HR. COOL TO 900F IN 75HR TVS APPROX 120

TABLE 4.11.2.1 (con't)

CONDITION	TITANIUM		YIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN)	DESIGN	CRACK LENGTH (IN)	2.5* (K(1C)/TYS) (IN)	K(1C) MEAN (KSI)	STAN DEV (KSI)	DATE	REF
	FORM	TEST ORIENT									
RECRYSTALLIZE AIRCAL	F	1.50	130.0	3.004	1.399	CT	1.987	81.70		1973	85034 (1)
		1.20	130.0	3.008	1.344	CT	1.653	92.60		1973	85857 (1)
		2.25	130.0	3.000	1.522	CT	1.522	94.50		1973	85034 (1)
		1.20	131.0	3.005	1.375	CT	1.599	76.30		1973	85857 (1)
		2.20	131.0	3.006	1.497	CT	1.592	80.60		1973	85857 (1)
		1.50	132.0	3.000	1.409	CT	1.563	79.00		1973	85034 (1)
		1.20	133.0	3.006	1.374	CT	1.577	77.90		1973	85857 (1)
		2.25	134.0	2.998	1.499	CT	1.537	86.30		1973	85034 (1)
		1.20	134.0	3.009	1.380	CT	1.625	91.00		1973	85857 (1)
		1.20	136.0	3.007	1.377	CT	1.585	89.40	83.9/	1973	85857 (1)
RECRYSTALLIZE AIRCAL	F	4.60	118.0	3.000	1.500	CT	1.532	83.00		1974	89004 (2)
		6.70	121.0	3.001	1.502	CT	1.552	89.30		1973	85634 (1)
		6.70	122.0	3.000	1.502	CT	1.540	92.30		1973	85034 (1)
		4.75	122.0	3.000	1.500	CT	1.573	91.10		1973	85034 (1)
		6.70	122.0	2.997	1.501	CT	1.532	90.20		1973	85034 (1)
		4.60	122.0	3.001	1.500	CT	1.540	90.60		1973	85034 (1)
		4.75	124.0	3.005	1.502	CT	1.544	86.70		1973	85634 (1)
		6.70	125.0	3.001	1.501	CT	1.543	91.70	88.9/	1973	85034 (1)
								83.60	63.9/	1972	85034 (1)
STA	P	0.62	160.0	3.503	0.633	CT	1.831	40.30		1973	85856
		0.62	160.0	3.503	0.634	CT	1.801	43.50		1973	85856
		0.62	160.0	3.501	0.632	CT	1.790	44.00	42.6/	1973	85856
STA	F	2.00	126.9	2.000	2.000	--	---	92.32		----	R1003
STA	F	2.00	132.0	2.000	2.000	--	---	83.32		----	R1003
STA 1750F 1 HR. WQ. 1300F 2 HR. AC	F	2.50	142.0	2.000	1.000	CT	1.000	59.80		1974	88962
		2.50	142.0	2.000	1.000	CT	1.000	56.90		1974	88962
	2.50	142.0	2.000	1.000	CT	1.000	61.40	59.4/	2.3	1974	88962

NOTES:
 (1) RECRYSTALLIZE ANNEAL=1700F 4 HR. FC TO 1400F AT 100F/HR. COOL TO 900F IN 75HR
 (2) RECRYSTALLIZE ANNEAL=1700F 4 HR. FC TO 1400F AT 100F/HR. COOL TO 900F IN 75HR
 TYS APPROX. 120

TABLE 4.11.2.1 (con't)

CONDITION	TITANIUM		YIELD (NSI)	TEST SPECIMEN ORIENT	THICK (IN)	TEMP (F)	SPECIMEN WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	K(IIC) (KSI)	K(IIC) (KSI)	K(IIC) (KSI)	STAN DEV (IN)	DATE	REFER
	FORM	THICK (IN)														
1450F 1HR, AC	P	1.00	146.0	T-L		R.T.	1.000	CT		0.23	44.00				1981	MR001
1700F 6 HR, AC	F	1.40	118.0	L-T		R.T.	3.006	1.317	CT	1.605	74.10				1973	85857
1400F 6 HR, AC		1.40	119.0				3.002	1.365	CT	1.615	81.30				1973	85857
		1.40	119.0				3.002	1.231	CT	1.587	71.60				1973	85857
		1.40	119.0				3.004	1.350	CT	1.588	81.10				1973	85857
		1.40	119.0				3.003	1.301	CT	1.583	73.00				1973	85857
		1.40	120.0				3.002	1.290	CT	1.604	74.40	79.9/	4.2		1973	85857
1700F 6 HR, AC	F	1.40	126.0	T-L		R.T.	3.001	1.357	CT	1.564	86.30				1973	85857
1400F 6 HR, AC		1.40	126.0				3.002	1.311	CT	1.599	76.00				1973	85857
		1.40	127.0				3.004	1.353	CT	1.617	87.50				1973	85857
		1.40	129.0				3.006	1.325	CT	1.500	74.80				1973	85857
		1.40	129.0				3.005	1.279	CT	1.568	85.20				1973	85857
		1.40	129.0				3.006	1.336	CT	1.632	77.10	81.2/	5.8		1973	85857
1750F 1 HR, WQ	F	3.00	159.0	T-L		75	5.100	2.000	WOL	1.998	66.30				1966	76411
1000F 4 HR		3.00	159.0				5.100	2.000	WOL	2.091	70.00	68.2/	2.6		1966	76411
1750F 1 HR, WQ	F	3.00	153.0	T-L		40	5.100	2.000	WOL	2.088	76.80				1966	76411
1000F 4 HR		3.00	153.0				5.100	2.000	WOL	2.059	66.20	71.9/	7.5		1966	76411
1750F 1 HR, WQ	F	3.00	147.0	T-L		0	5.100	2.000	WOL	1.998	66.40				1966	76411
1000F 4 HR		3.00	147.0				5.100	2.000	WOL	2.081	72.90	69.7/	4.6		1966	76411
1750F 1 HR, WQ	F	3.00	148.0	T-L		32	5.100	2.000	WOL	2.041	64.40				1966	76411
1000F 4 HR		3.00	148.0				5.100	2.000	WOL	2.011	65.30	63.0/	0.8		1966	76411
1750F 1 HR, WQ	F	3.00	140.0	T-L		R.T.	5.100	2.000	WOL	1.986	84.90				1966	76411
1000F 4 HR		3.00	140.0				5.100	2.000	WOL	2.019	76.60				1966	76411
		3.00	140.0				5.100	2.000	WOL	2.010	76.30	79.3/	4.9		1966	76411
1750F 1 HR, WQ	F	3.00	133.0	T-L		100	5.100	2.000	WOL	1.969	72.90				1966	76411
1000F 4 HR		3.00	133.0				5.100	2.000	WOL	2.049	67.30	71.1/	2.5		1966	76411

TABLE 4.11.2.1 (con't)

CONDITION	TITANIUM		TI-6AL-4V	K(1C)	--PHOSPHOR--		TEST SPECIMEN		YIELD STRENGTH (KSI)	WIDTH (IN)	SPECIMEN		CRACK LENGTH (IN)	2.5% CRACK (K(1C)/TVS)**2 (IN)	K(1C) MEAN DEV (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER
	FORM	THICK (IN)			THICK (IN)	DESIGN	THICK (IN)	DESIGN			W	R						
1750F 1 HR. WQ. 1000F 4 HR	F	3 00	150	Y-L	127.0	5 100	2 000	WOL	1 970	0 85	74.00	1966	76411					
		3 00			127.0	5 100	2 000	WOL	2 033	1 00	82.00	1966	76411					
1750F 1HR.FC TO 1100F.AC	P	1 50	R.T.	L-T	120.0	4 003	1 501	CT	1 991	1 20	83.00	1973	85836					
1750F 1HR.FC TO 1100F.AC	P	1 50	R.T.	T-L	120.0	4 004	1 501	CT	1 938	1 41	70.00	1973	85836					
		1 50			120.0	4 000	1 500	CT	----	1 50	93.00	1974	85004					
1750F 1HR.FC TO RT	P	1 50	R.T.	L-T	120.0	4 004	1 502	CT	1 717	0 84	69.50	1973	85836					
		1 50			120.0	4 004	1 501	CT	1 718	0 95	74.00	1973	85836					
1750F 1HR.FC TO RT	P	1 50	R.T.	T-L	120.0	4 008	1 502	CT	1 956	1 43	90.60	1973	85836					
		1 50			120.0	4 003	1 502	CT	1 986	1 49	92.90	1973	85836					
1750F 2 HR.FC TO 900F AT 100F/1HR.AC	F	3 00	R.T.	L-T	115.0	3 003	1 500	CT	1 716	1 20	79.80	1973	88440					
1750F 2 HR.FC TO 900F AT 100F/1HR.AC	F	3 00	R.T.	T-L	130.0	3 003	1 500	CT	1 581	1 21	90.90	1973	88440					
1750F 2HR.WQ. 1000F 2HR.AC. 1350F 2HR.AC.STA	P	0 62	R.T.	L-T	150.0	3 501	0 634	CT	1 865	0 17	39.80	1973	85836					
		0 62			150.0	3 501	0 633	CT	1 880	0 20	43.00	1973	85836					
											41.4/	2.3						
1500F. 0 9HR. AC 1350F. 21MS. AC	P	1 00	R.T.	T-L	126.0	----	1 000	CT	----	1 44	95.60	1981	NR001					

TABLE 4.11.2.2

TITANIUM		TI-6AL-4V		K(C)		CRACK LENGTH		CROSS STRESS		K(I) STAN		K(I) STAN						
CONDITION	PRODUCT-- FORM	THICK (IN)	TEST SPEC OR STR (F)	THICK (IN)	YIELD (KSI)	SPECIMEN--		CRACK LENGTH		CROSS STRESS		K(I) STAN						
						WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)	ORIBET (KSI)	MAX (KSI)	K (APP) (KSI)	MEAN (KSI)	DEV (KSI)	STAN (IN)	MEAN (KSI)	DEV (KSI)	DATE REFER
ANNEALED	S	0.04	109	L-T	163.0	8.000	0.040	3.060	---	47.40	114.42	---	---	---	---	---	1963	54304
	0.04	163.0	B.000	0.040	1.040	---	---	---	94.10	121.54	---	---	---	---	---	---	1963	54304
	0.04	163.0	B.000	0.040	0.890	---	---	---	101.00	117.52	---	---	---	---	---	---	1963	54304
	0.04	163.0	B.000	0.040	1.340	---	---	---	77.20	122.89	---	---	---	---	---	---	1963	54304
	0.04	163.0	B.000	0.040	2.000	---	---	---	73.60	135.72	---	---	---	---	---	---	1963	54304
0.04	163.0	B.000	0.040	4.840	---	---	---	33.60	121.50	---	---	---	---	---	---	1963	54304	
0.04	163.0	B.000	0.040	4.440	---	---	---	35.30	116.22	121.4	7.0	---	---	---	---	1963	54304	
ANNEALED	B	0.04	R.T.	L-T	137.3	8.000	0.040	4.050	---	47.50	143.18	---	---	---	---	---	1963	54304
	0.04	137.3	B.000	0.040	3.030	---	---	---	36.20	137.12	---	---	---	---	---	---	1963	54304
	0.04	137.3	B.000	0.040	2.030	---	---	---	78.60	145.78	---	---	---	---	---	---	1963	54304
	0.04	137.3	B.000	0.040	0.930	---	---	---	108.30	133.46*	---	---	---	---	---	---	1963	54304
	0.04	137.3	B.000	0.040	1.950	---	---	---	95.50	152.56*	---	---	---	---	---	---	1963	54304
0.04	137.3	B.000	0.040	3.030	---	---	---	61.20	146.71	---	---	---	---	---	---	1963	54304	
0.04	137.3	B.000	0.040	0.480	---	---	---	126.00	109.63*143.2	4.3	---	---	---	---	---	1963	54304	
ANNEALED	S	0.04	590	L-T	96.7	8.000	0.040	0.250	---	111.20	69.73*	---	---	---	---	---	1963	54304
	0.04	96.7	B.000	0.040	1.260	---	---	---	91.00	130.02*	---	---	---	---	---	---	1963	54304
	0.04	96.7	B.000	0.040	0.570	---	---	---	101.20	96.06*	---	---	---	---	---	---	1963	54304
	0.04	96.7	B.000	0.040	0.950	---	---	---	94.90	116.95*	---	---	---	---	---	---	1963	54304
	0.04	96.7	B.000	0.040	2.020	---	---	---	80.50	149.31*	---	---	---	---	---	---	1963	54304

BUCKLING OF CRACK EDGES RESTRAINED

TITANIUM		TI-6AL-4V		K(C)		CRACK LENGTH		CROSS STRESS		K(I) STAN		K(I) STAN						
CONDITION	PRODUCT-- FORM	THICK (IN)	TEST SPEC OR STR (F)	THICK (IN)	YIELD (KSI)	SPECIMEN--		CRACK LENGTH		CROSS STRESS		K(I) STAN						
						WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)	ORIBET (KSI)	MAX (KSI)	K (APP) (KSI)	MEAN (KSI)	DEV (KSI)	STAN (IN)	MEAN (KSI)	DEV (KSI)	DATE REFER
MA	P	0.25	R.T.	L-T	130.0	9.630	0.266	3.780	6.860	18.70	37.80	148.60	---	---	---	---	1971	83984
	0.25	130.0	9.630	0.266	3.800	5.220	23.60	51.70	140.00	---	---	---	---	---	---	---	1971	83984
	0.25	130.0	9.630	0.293	1.920	---	---	36.50	85.10	151.32*144.3	6.1	---	---	---	---	---	1971	83984
MA	P	0.25	R.T.	L-T	130.0	16.110	0.289	12.930	13.950	11.30	15.40	125.65	---	---	---	---	1971	83984
MA	P	0.25	R.T.	L-T	130.0	16.120	0.240	8.020	10.580	31.30	45.10	189.99	---	---	---	---	1971	83984
0.25	130.0	16.120	0.275	3.990	6.100	31.10	67.50	175.67	182.8/10.1	229.36*	---	---	---	---	---	1971	83984	

*NOTE - NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 4.11.2.2 (con't)

CONDITION	TITANIUM	TI-6AL-4V	K(C)	SPECIMEN	CRACK LENGTH GRIPS STRESS			K(APP) STAN	K(C)	STAN										
					WIDTH (IN)	THICK B	YIELD STR (KSI)				INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	MEAN DEV (KSI)	DEV (IN)	REFER			
HA	P	R T	L-T	0.25	0.25	130.0	0.265	4.540	---	53.90	73.30	209.36	---	---	---	---	---	1971	83984	
		0.25	0.25	130.0	0.265	4.640	---	55.60	75.40	212.53	210.8	2.1	---	---	---	---	---	---	1971	83984
HA	P	R T	L-T	0.25	0.25	130.0	0.275	8.010	---	30.60	38.90	217.31	---	---	---	---	---	---	1971	83984
		0.25	0.25	130.0	0.275	19.200	21.700	14.20	26.20	187.13	---	---	218.88	---	---	---	---	---	1971	83984
HA	P	R T	L-T	0.25	0.25	130.0	0.270	12.720	17.000	33.40	47.00	233.00	212.5	23.3	295.74	297.3	3/94	3	1971	83984
		0.25	0.25	130.0	0.262	6.020	---	39.20	73.20	236.38	---	---	---	---	---	---	---	---	1971	83984

BUCKLING OF CRACK EDGES UNKNOWN

BUCKLING OF CRACK EDGES RESTRAINED

CONDITION	TITANIUM	TI-6AL-4V	K(C)	SPECIMEN	WIDTH (IN)	THICK B	YIELD STR (KSI)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) STAN	K(C)	STAN									
															MEAN DEV (KSI)	DEV (IN)	REFER						
HA	S	R T	L-T	0.05	0.05	136.5	0.049	5.990	---	47.30	150.98	---	---	---	---	---	---	---	---	1964	57573		
		0.05	0.05	136.5	0.050	6.000	---	47.90	151.72	---	---	---	---	---	---	---	---	---	---	---	1964	57573	
		0.05	0.05	133.8	0.048	6.000	6.950	91.80	52.10	166.39	---	---	175.22	---	---	---	---	---	---	---	---	1964	57573
		0.05	0.05	133.8	0.030	6.000	---	41.30	31.50	164.46	---	---	---	---	---	---	---	---	---	---	---	1964	57573
		0.05	0.05	136.5	0.049	6.000	---	60.70	193.83	---	---	---	---	---	---	---	---	---	---	---	---	1964	57573
		0.05	0.05	136.5	0.049	6.000	10.500	43.60	69.60	198.39	---	---	228.95	---	---	---	---	---	---	---	---	1964	57573
		0.05	0.05	136.5	0.030	3.000	---	78.80	172.72	---	---	---	---	---	---	---	---	---	---	---	---	1964	57573
		0.05	0.05	136.5	0.047	10.000	---	41.60	184.97	---	---	---	---	---	---	---	---	---	---	---	---	1964	57573
		0.05	0.05	136.5	0.030	6.000	---	56.60	180.74	---	---	---	---	---	---	---	---	---	---	---	---	1964	57573
		0.05	0.05	136.7	0.032	6.010	7.350	41.10	31.80	165.57	---	---	186.87	---	---	---	---	---	---	---	---	1964	57573
		0.05	0.05	136.7	0.030	6.000	---	53.20	169.88	---	---	---	---	---	---	---	---	---	---	---	---	1964	57573
		0.05	0.05	136.7	0.032	6.010	8.750	43.80	31.40	164.29	---	---	207.75	---	---	---	---	---	---	---	---	1964	57573
HA	S	R T	L-T	0.05	0.05	136.0	0.035	6.010	8.170	45.90	31.90	164.60	---	---	---	---	---	---	---	---	1964	57573	
		0.05	0.05	136.0	0.034	6.000	8.120	30.40	47.00	190.08	167.0	12.8	180.69	196.4	1/79	9	1964	57573					
HA	S	R T	L-T	0.05	0.05	136.7	0.032	5.990	---	54.20	172.73	---	---	---	---	---	---	---	---	---	1964	57573	
HA	S	R T	L-T	0.20	0.20	127.3	0.212	6.000	---	81.00	238.66*	---	---	---	---	---	---	---	---	---	1964	57573	
		0.20	0.20	127.3	0.218	6.000	---	76.40	243.96	---	---	---	---	---	---	---	---	---	---	---	1964	57573	

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 4.11.2.2 (con't)

TITANIUM		TI-6AL-4V		K(C)		CRACK LENGTH GROSS STRESS													
CONDITION	--PRODUCT-- FORM THICK TEMP OR (IN) (F)	TEST SPEC YIELD STR (KSI)	WIDTH (IN)	THICK (IN)	SPECIMEN M B	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K (APP) (KSI*SQRT IN)	K (APP) (KSI*SQRT IN)	STAN DEV	K (C) (KSI*SQRT IN)	STAN DEV	K (C) (KSI*SQRT IN)	STAN DEV	DATE	REFER	
																			2A(D)
MA	S	0.20	R. T.	L-T	129.3	24.070	0.212	3.010	---	93.10	204.41*	---	---	---	---	---	---	---	1964 57573
		0.20			129.3	24.080	0.220	10.000	---	55.30	245.86	238.9/11.2	---	---	---	---	---	---	1964 57573
MA	S	0.05	82	L-T	136.5	24.070	0.051	5.990	7.100	43.30	47.50	151.53	167.72						1964 57573
MA	S	0.05	- 110	T-L	163.3	8.000	0.050	1.980	3.130	35.00	84.70	155.28	207.78*						1964 57573
		0.05			163.3	8.010	0.050	1.970	2.540	72.50	77.30	141.29	164.74						1964 57573
		0.05			164.3	8.010	0.032	1.920	2.370	66.60	75.50	132.97	144.2/10.0	154.07	159.4/ 7.5				1964 57573
MA	S	0.03	R. T.	T-L	127.0	8.040	0.025	1.980	2.600	61.20	75.60	138.54	163.45*						1964 57573
MA	S	0.05	R. T.	T-L	136.0	8.010	0.052	2.000	2.220	90.00	95.30	175.72*	186.89*						1964 57573
MA	S	0.13	R. T.	T-L	139.7	8.050	0.127	1.980	2.740	48.00	103.70	170.02*	231.93*						1964 57573
MA	S	0.03	650	F-L	80.2	8.030	0.025	2.060	2.460	75.70	77.70	145.73*	165.23*						1964 57573
MA	S	0.05	650	T-L	81.7	8.020	0.031	2.000	2.090	63.40	75.40	139.01*	142.64*						1964 57573

BUCKLING OF CRACK EDGES RESTRAINED

BUCKLING OF CRACK EDGES NOT RESTRAINED																				
CONDITION	FORM	THICK	TEMP	OR	YIELD STR	WIDTH	THICK	INIT	FINAL	ONSET	MAX	K (APP)	K (APP)	STAN	DEV	K (C)	STAN	DEV	DATE	REFER
13GOF 1HR.AC	F	---	R. T.	L-T	147.1	5.970	0.382	2.020	3.200	---	53.50	102.64	146.98							1964 58782
		---			147.1	5.970	0.382	2.020	3.180	---	51.90	99.57	101.1/ 2.2	141.72	144.4/ 3.7					1964 58782
13GOF 1HR.AC	F	---	R. T.	L-T	147.1	8.970	0.732	3.000	5.000	---	54.40	126.94	190.38*							1964 58782
13GOF 1HR.AC	F	---	R. T.	L-T	147.1	8.970	0.998	3.000	5.200	---	28.30	64.05	103.28							1964 58782

-NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 4.11.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION:					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K MIN	A:	6.09	.129		
	B:				
	C:				
	D:				
		7.00	.238		
	8.00	.340			
	9.00	.572			
	10.00	1.36			
DELTA K MAX	A:	12.31	2.80		
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		12.09			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT:
 FORM:
 SPECIMEN TYPE:
 ORIENTATION:
 STRESS RATIO: +0.10
 FREQUENCY: 30.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.081"
 SPECIMEN WIDTH: 2.500"
 REFERENCES:PW003

TITAN.
 ALLOY
 TI-6AL-
 4V

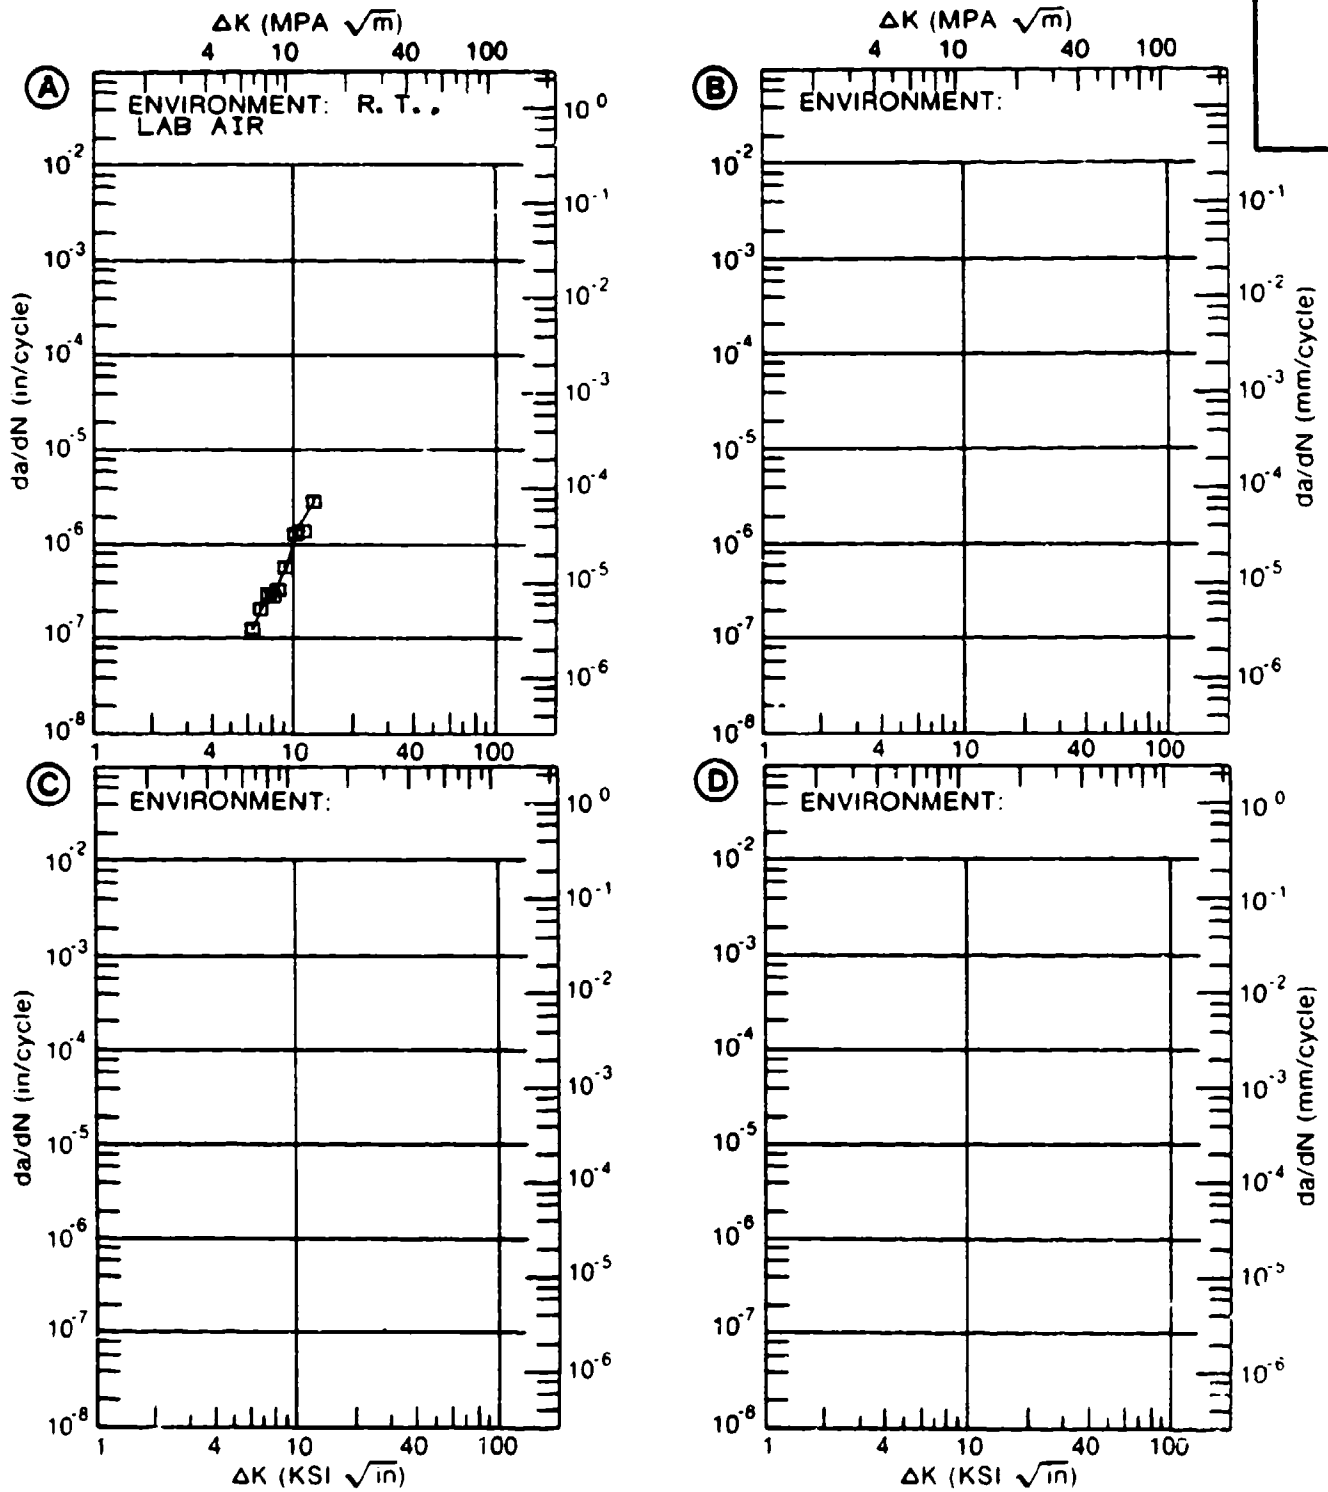


Figure 4.11.3.1

TABLE 4.11.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.2 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION:					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN. /CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 30	R=+0. 50	R=+0. 70
DELTA K	A: 11.07	1.31			
MIN	B: 7.27		.201		
	C: 5.18			.0883	
	D: 3.07				.0336
	3.50				.0473
	4.00				.0707
	5.00				.152
	6.00			.165	.300
	7.00			.334	.544
	8.00		.400	.656	1.04
	9.00		.904	1.14	
	10.00		1.65	1.81	
	13.00	2.86	4.56	5.34	
	16.00	5.86	8.52	12.1	
	20.00	10.4	17.0		
	25.00	17.8			
	30.00	31.2			
	35.00	58.9			
	40.00	121.			
DELTA K	A: 41.03	142.			
MAX	B: 21.70		20.4		
	C: 18.26			18.5	
	D: 8.80				1.80
ROOT MEAN SQUARE		12.53	16.74	28.71	12.56
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT:
 FORM:
 SPECIMEN TYPE: CT
 ORIENTATION: C-R
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.280 - 0.299"
 SPECIMEN WIDTH: 2.500"
 REFERENCES PW003

TITAN.
 ALLOY
 TI-6AL-
 4V

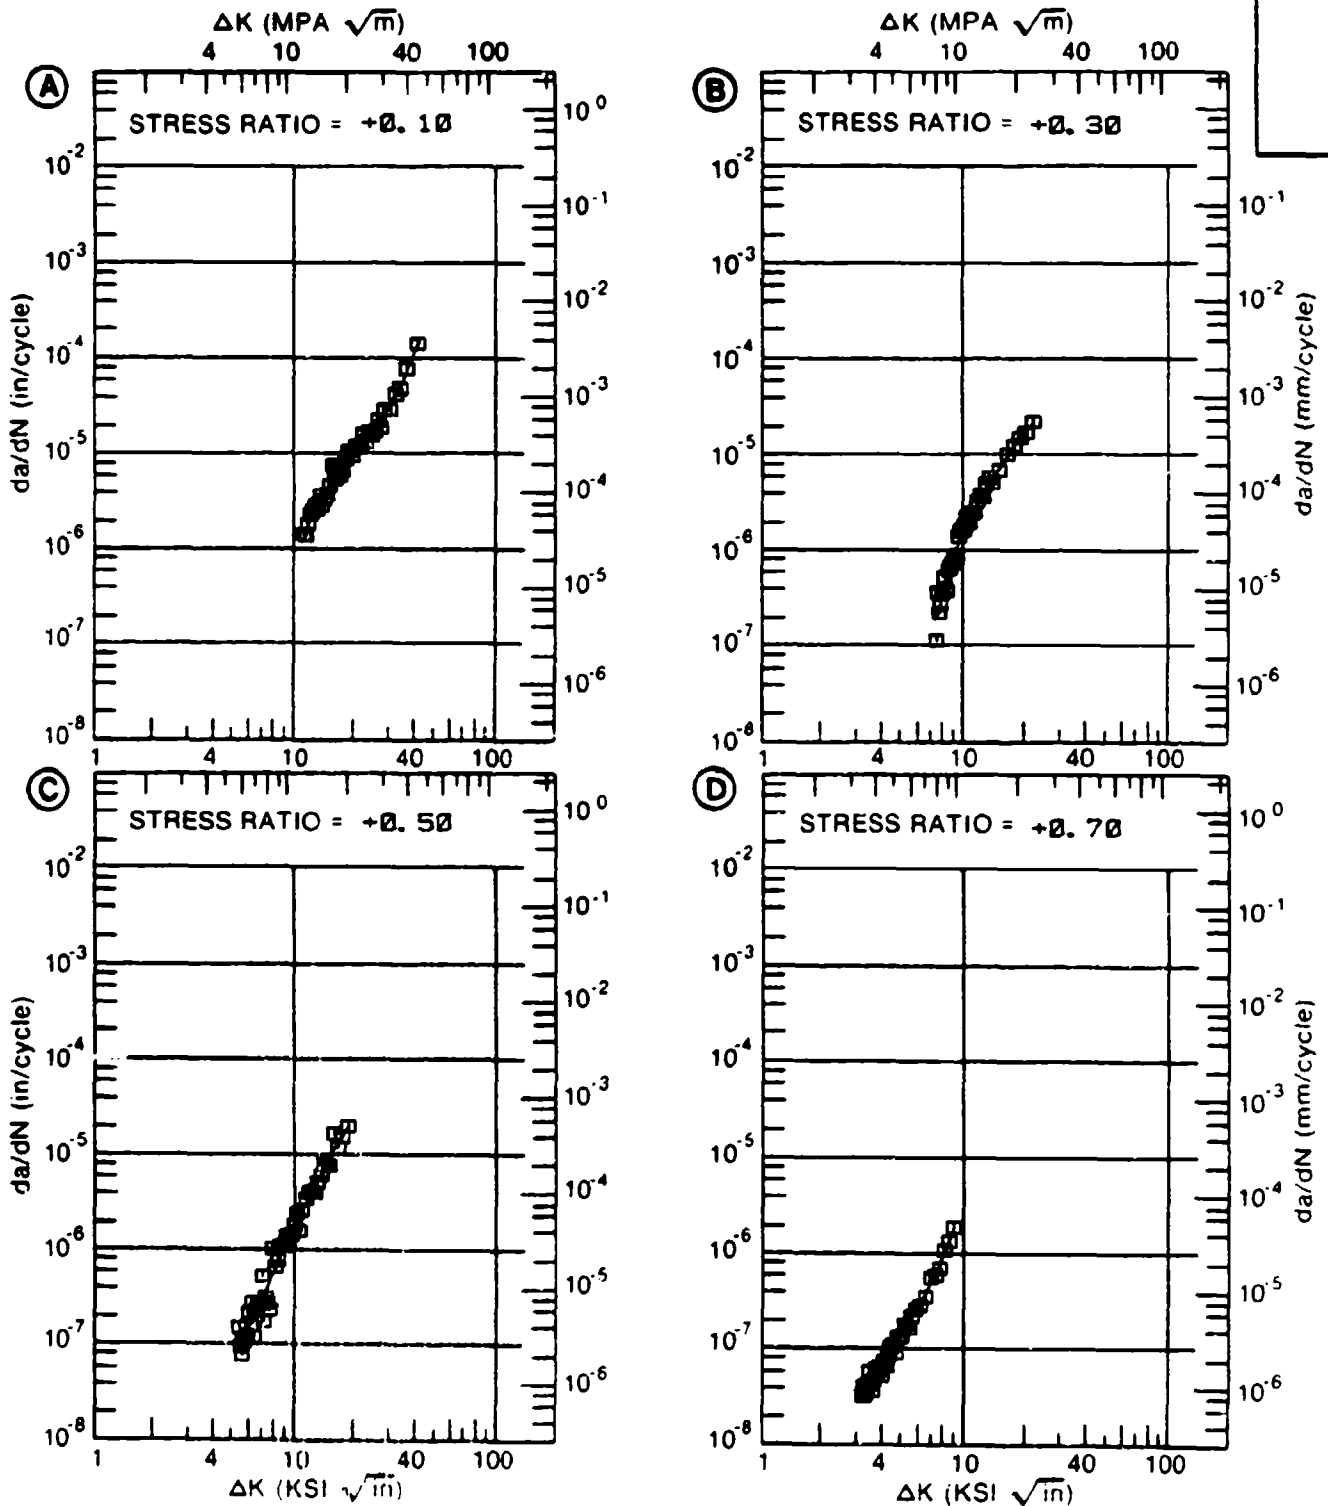


Figure 4.11.3.2

TABLE 4.11.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION:					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.	E=+ 300F		
		LAB AIR	AIR		
DELTA K	A: 8.55	.799			
MIN	B: 8.26		.885		
	C:				
	D:				
	9.00	.849	.976		
	10.00	1.13	1.26		
	13.00	4.02	3.60		
	16.00	12.1	9.07		
DELTA K	A: 17.54	20.1			
MAX	B: 18.42		15.0		
	C:				
	D:				
ROOT MEAN SQUARE		11.07	23.47		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT:
 FORM:
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 STRESS RATIO: -1.00
 FREQUENCY: 0.16 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.297- 0.301"
 SPECIMEN WIDTH: 2.500"
 REFERENCES: PW003

TITAN.
 ALLOY
 TI-6AL-
 4V

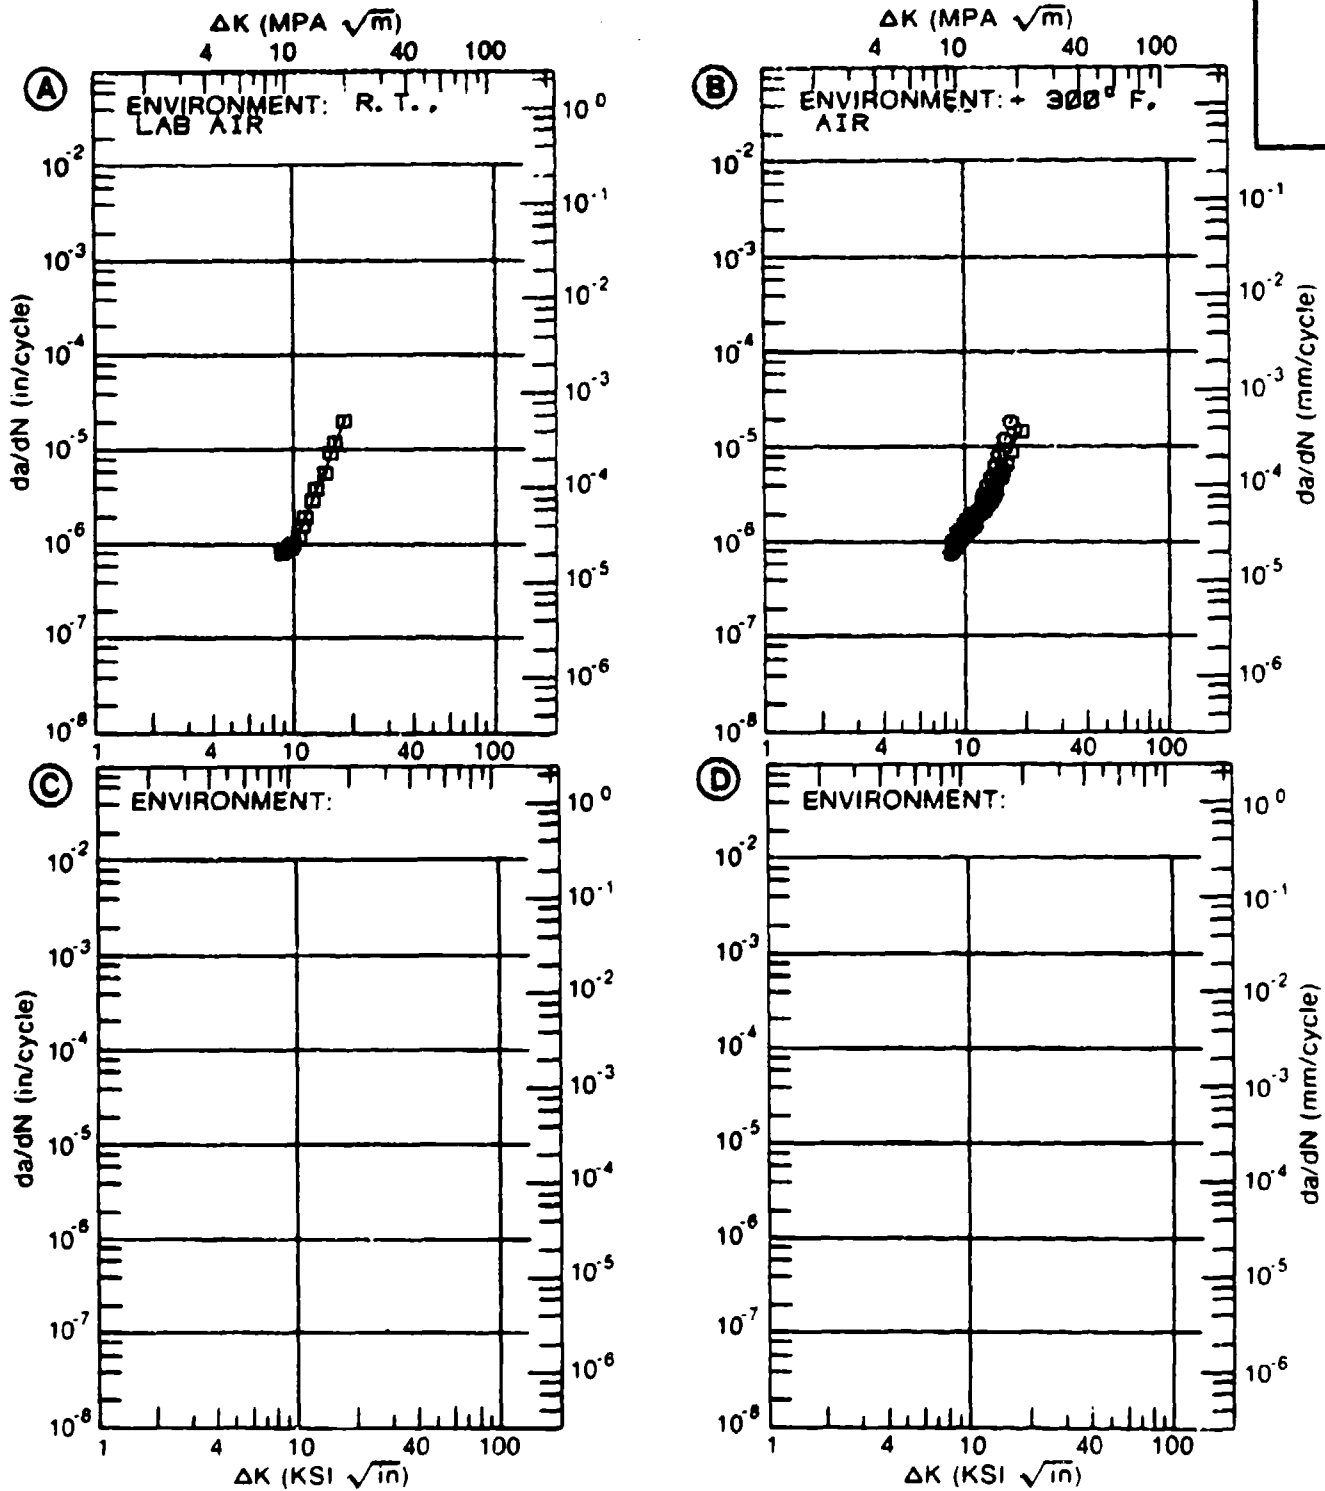


Figure 4.11.3.3

TABLE 4.11.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.4 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION:					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E=+ 300F AIR		
DELTA K	A: 8.19	.424			
MIN	B: 8.12		.208		
	C:				
	D:				
	9.00	.695	.495		
	10.00	1.14	.971		
	13.00	3.68	2.95		
	16.00	11.3	6.42		
DELTA K	A: 16.57	14.2			
MAX	B: 18.48		13.6		
	C:				
	D:				
ROOT MEAN SQUARE		17.73	27.56		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT:
 FORM:
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 STRESS RATIO: -0.50
 FREQUENCY: 0.10 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.301 - 0.302"
 SPECIMEN WIDTH: 2.500"
 REFERENCES: PW003

TITAN.
 ALLOY

TI-6AL-
 4V

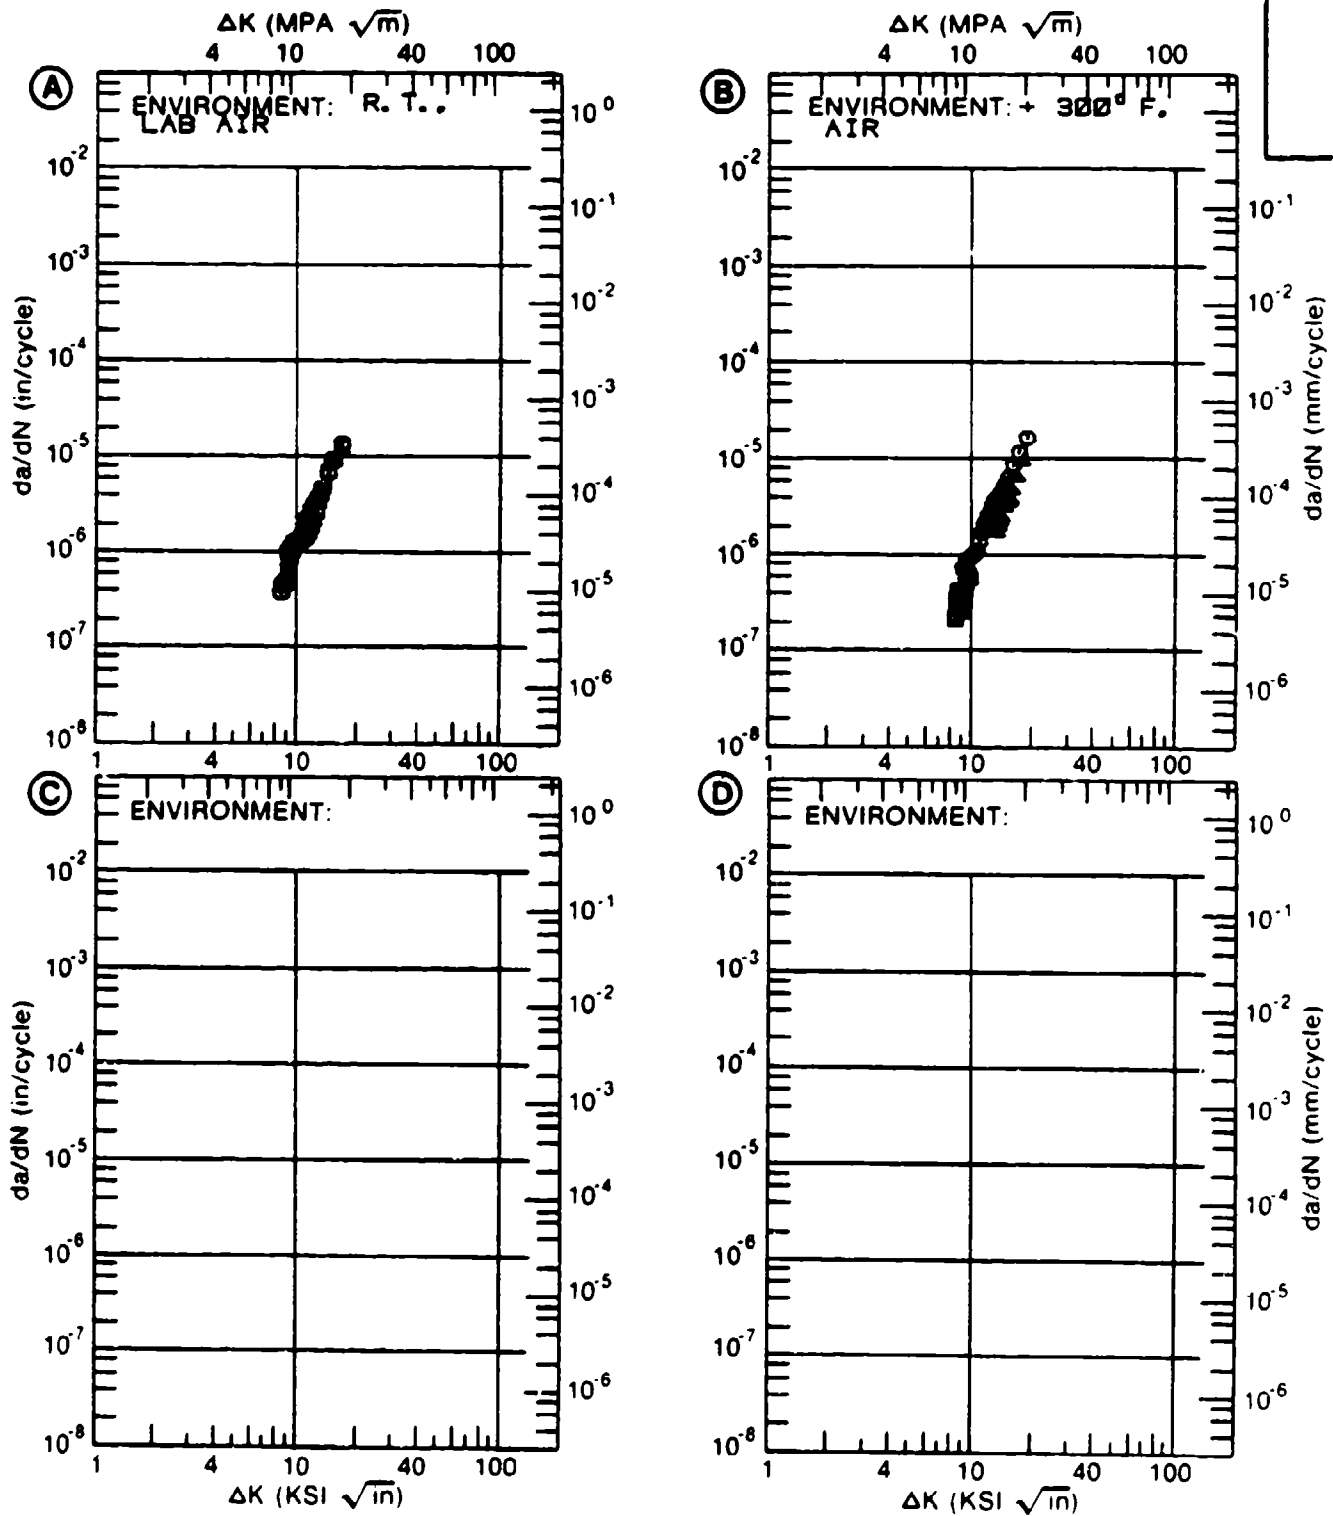


Figure 4.11.3.4

TABLE 4.11.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.5 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: ANNEALED
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.02			
DELTA K	A: 9.04	.135			
MIN	B:				
	C:				
	D:				
	10.00	.270			
	13.00	1.30			
	16.00	3.67			
	20.00	9.49			
	25.00	21.3			
	30.00	38.2			
	35.00	60.1			
	40.00	87.2			
DELTA K	A: 44.93	120.			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 24.21
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8 1
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: ANNEALED
 FORM: 8.00" TH BILLET
 SPECIMEN TYPE: WOL
 ORIENTATION: L-T
 FREQUENCY: 10.00- 20.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 123.0 KSI
 ULT. STRENGTH: 135.0 KSI
 SPECIMEN THK: 1.250"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: MA003

TITAN,
 ALLOY

TI-6AL-
 4V

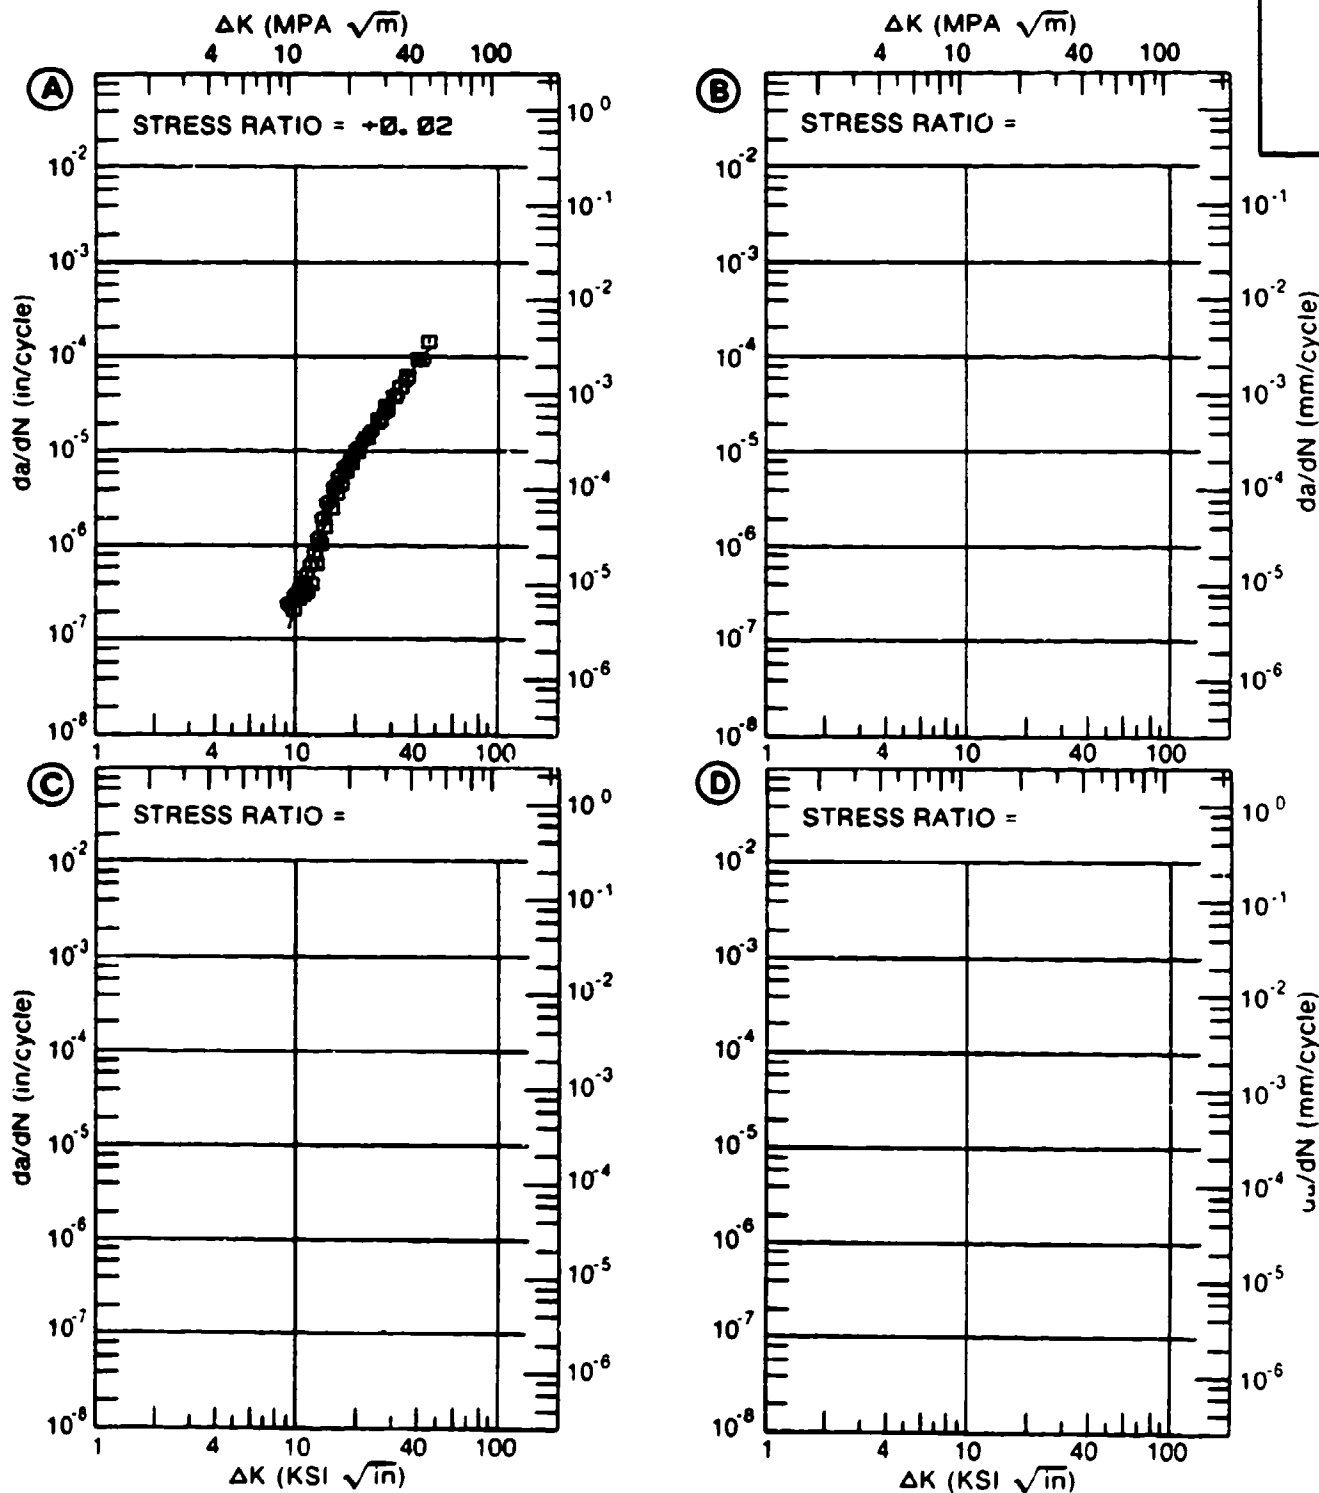


Figure 4.11.3.5

TABLE 4.11.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.6 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: ANNEALED AT 1375F, 3HRS, AC
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.02			
DELTA K	A: 8.52	.0853			
MIN	B:				
	C:				
	D:				
	9.00	.131			
	10.00	.283			
	13.00	1.41			
	16.00	3.88			
	20.00	9.70			
	25.00	21.7			
	30.00	40.8			
	35.00	70.2			
	40.00	116.			
DELTA K	A: 42.37	145.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		25.31			
PERCENT ERROR					

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	2
RATIO	0.8-1.25	
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: ANNEALED AT 1375F, 3HRS, AC

FORM: 2.75" TH PLATE

SPECIMEN TYPE: WOL

ORIENTATION: L-T

FREQUENCY: 10.00- 20.00 HZ

ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 120.0 KSI

ULT. STRENGTH: 130.0 KSI

SPECIMEN THK: 1.250"

SPECIMEN WIDTH: 5.000"

REFERENCES MA003

TITAN.
ALLOY

TI-6AL-
4V

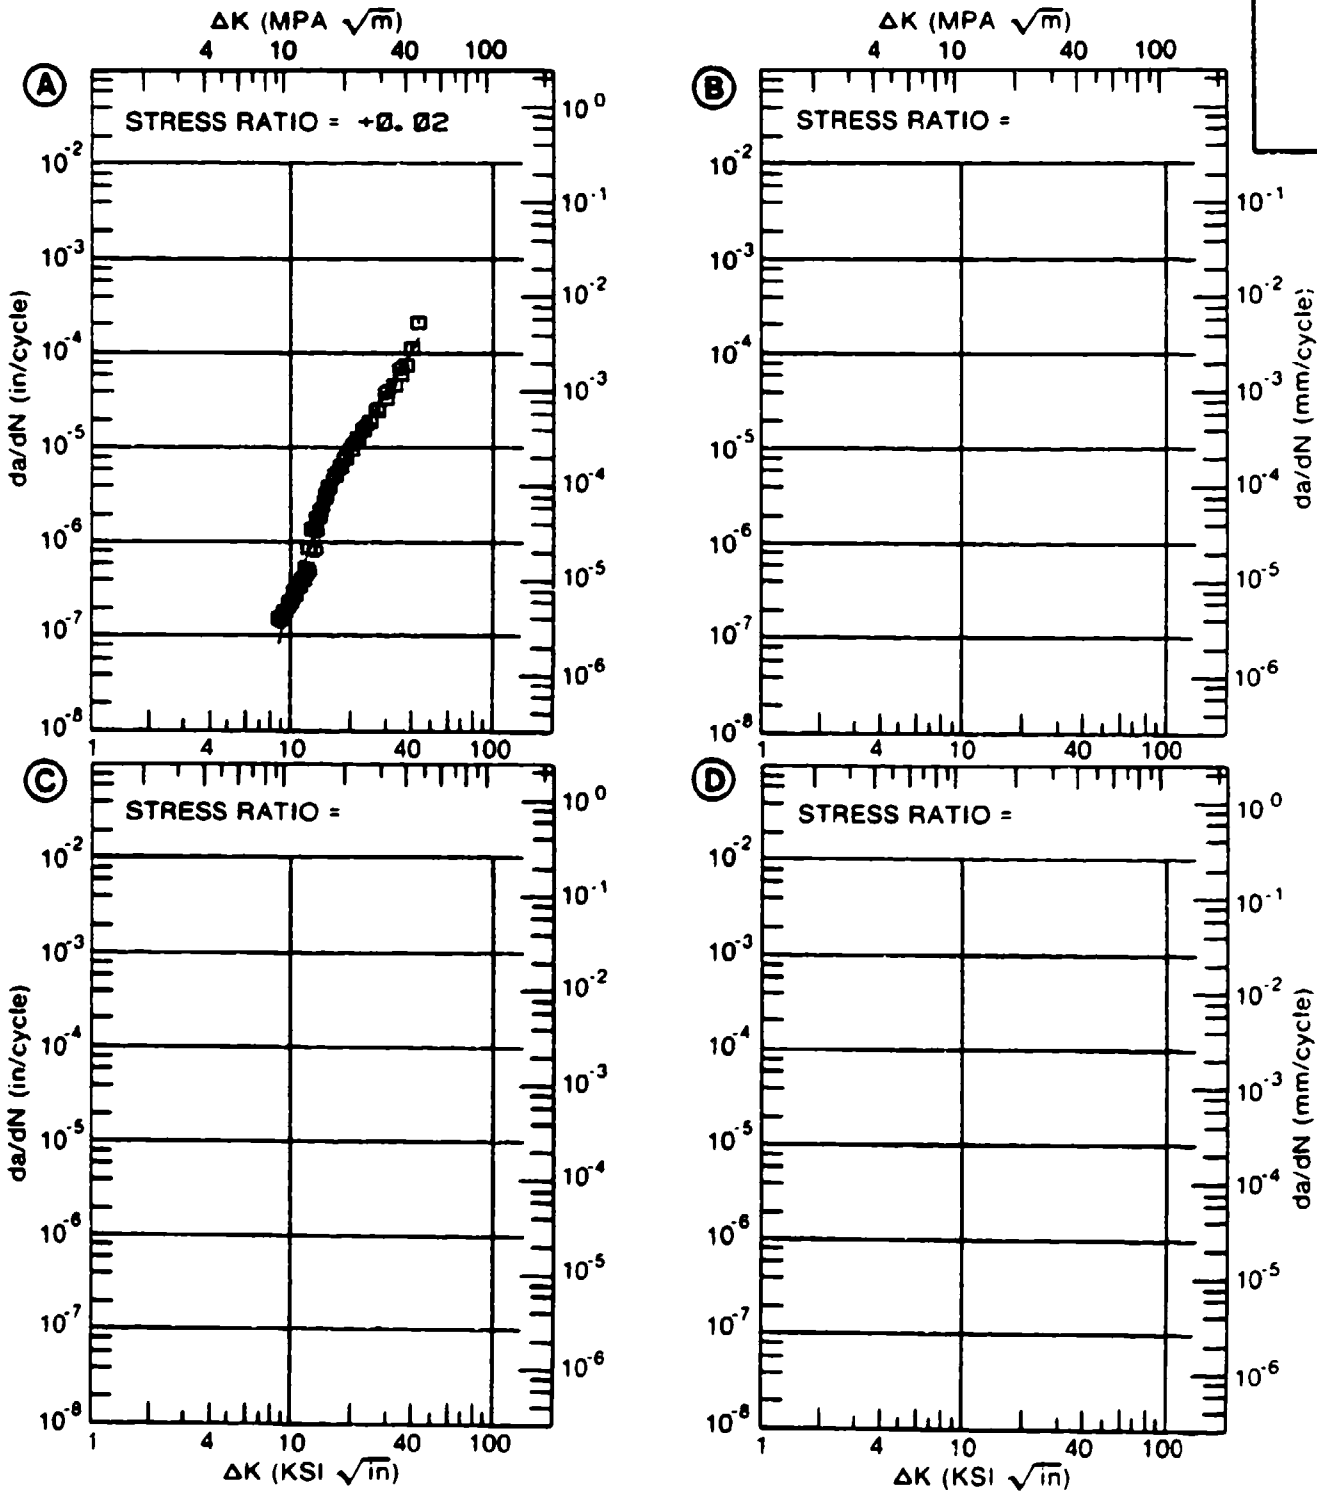


Figure 4.11.3.6

TABLE 4.11.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.7 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A: 5.13	1.45			
	B:				
	C:				
	D:				
	6.00	1.91			
	7.00	2.47			
	8.00	3.10			
DELTA K MAX	9.00	3.82			
	10.00	4.66			
	13.00	8.43			
	16.00	15.4			
	A: 18.19	24.2			
	B:				
	C:				
D:					
ROOT MEAN SQUARE		16.35			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 0.05" TH SHEET
 SPECIMEN TYPE: CT
 ORIENTATION:
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 130.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.050"
 SPECIMEN WIDTH: 3.940"
 REFERENCES: NL001

TITAN.
 ALLOY
 TI-6AL-
 4V

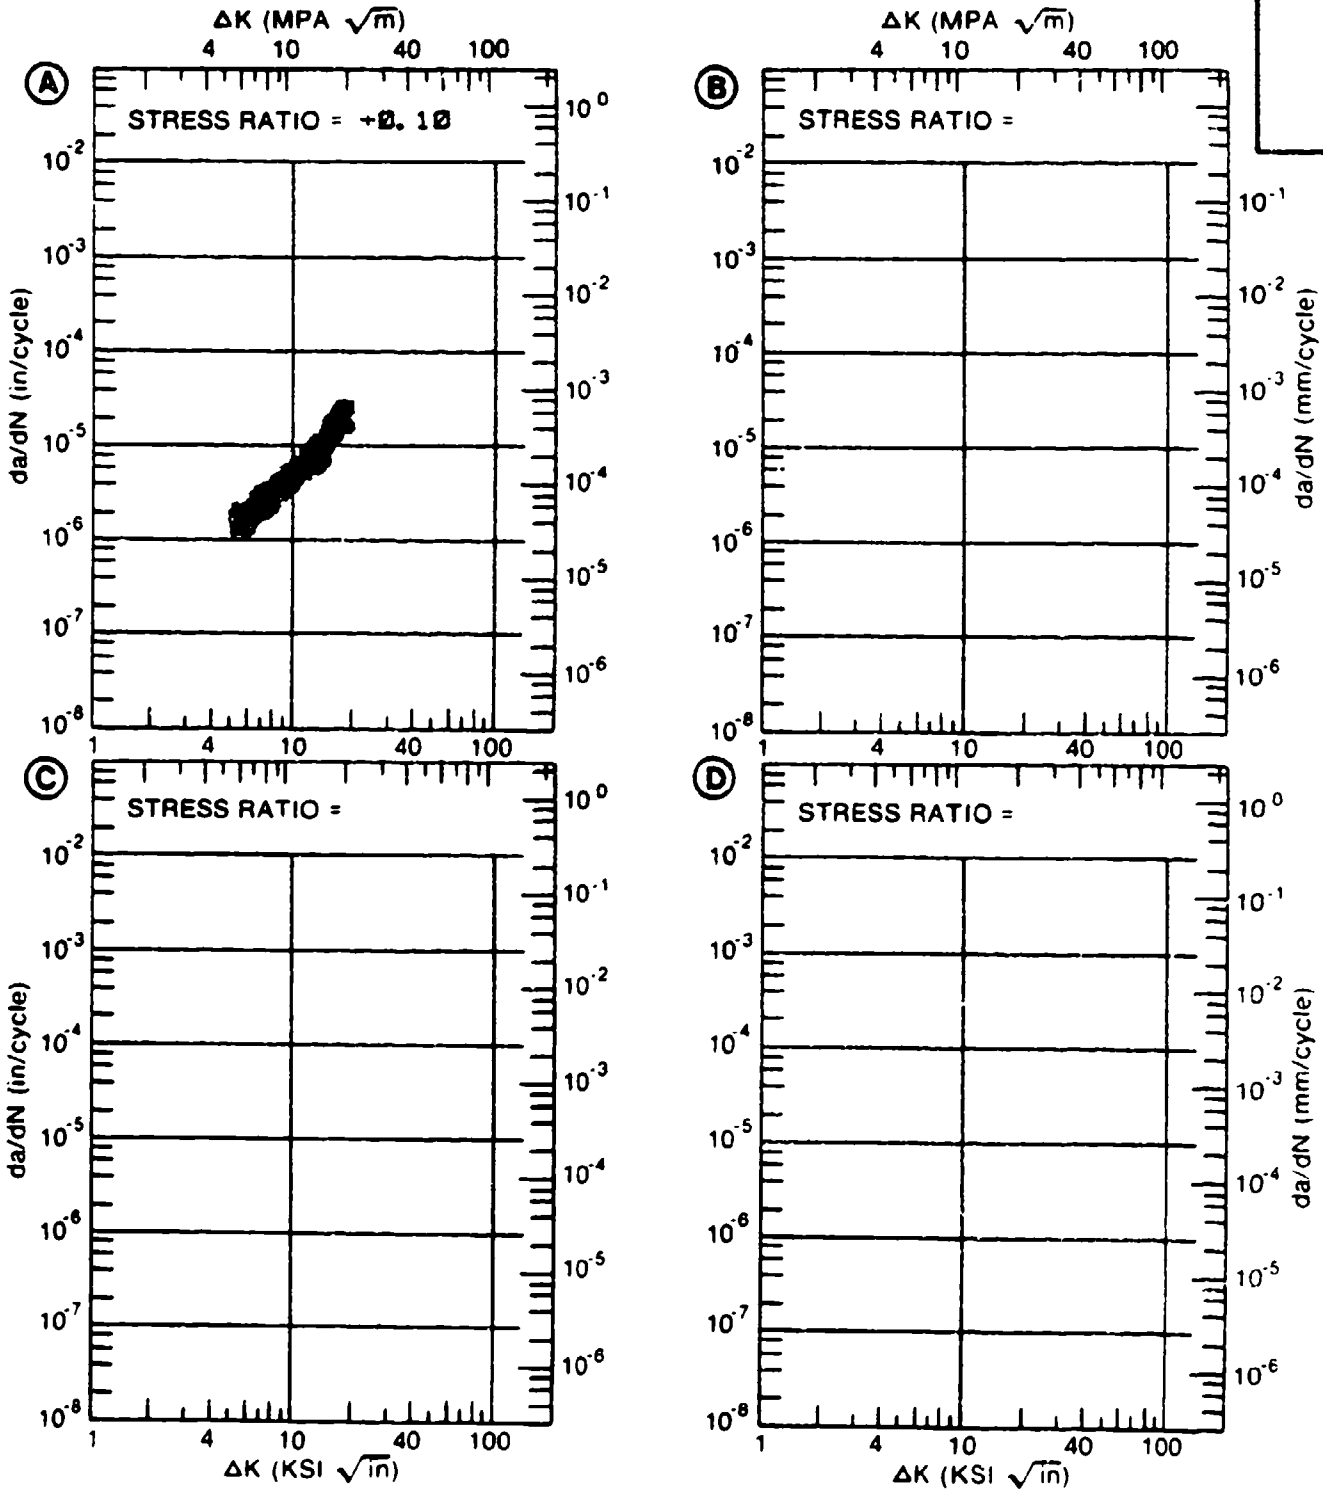


Figure 4.11.3.7

TABLE 4.11.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.8 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.30	R=+0.70	
DELTA K A:	9.98	1.84			
MIN B:	17.87		10.4		
C:	9.03			2.34	
D:					
	10.00	1.86		3.90	
	13.00	4.87		9.31	
	16.00	8.71		14.6	
	20.00	14.5	15.1	24.4	
	25.00	22.7	26.9	53.8	
	30.00	32.7	40.7	150.	
	35.00	45.7	59.7		
	40.00	63.2	89.2		
	50.00	121.	224.		
	60.00	238.			
	70.00	476.			
DELTA K A:	71.28	521.			
MAX B:	59.74		643.		
C:	33.00			311.	
D:					
ROOT MEAN SQUARE		8.97	11.51	15.91	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	2	1	1	
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 0.05" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION:
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 130.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.050"
 SPECIMEN WIDTH: 3.150"
 REFERENCES: NL001

TITAN.
 ALLOY
 TI-6AL-
 4V

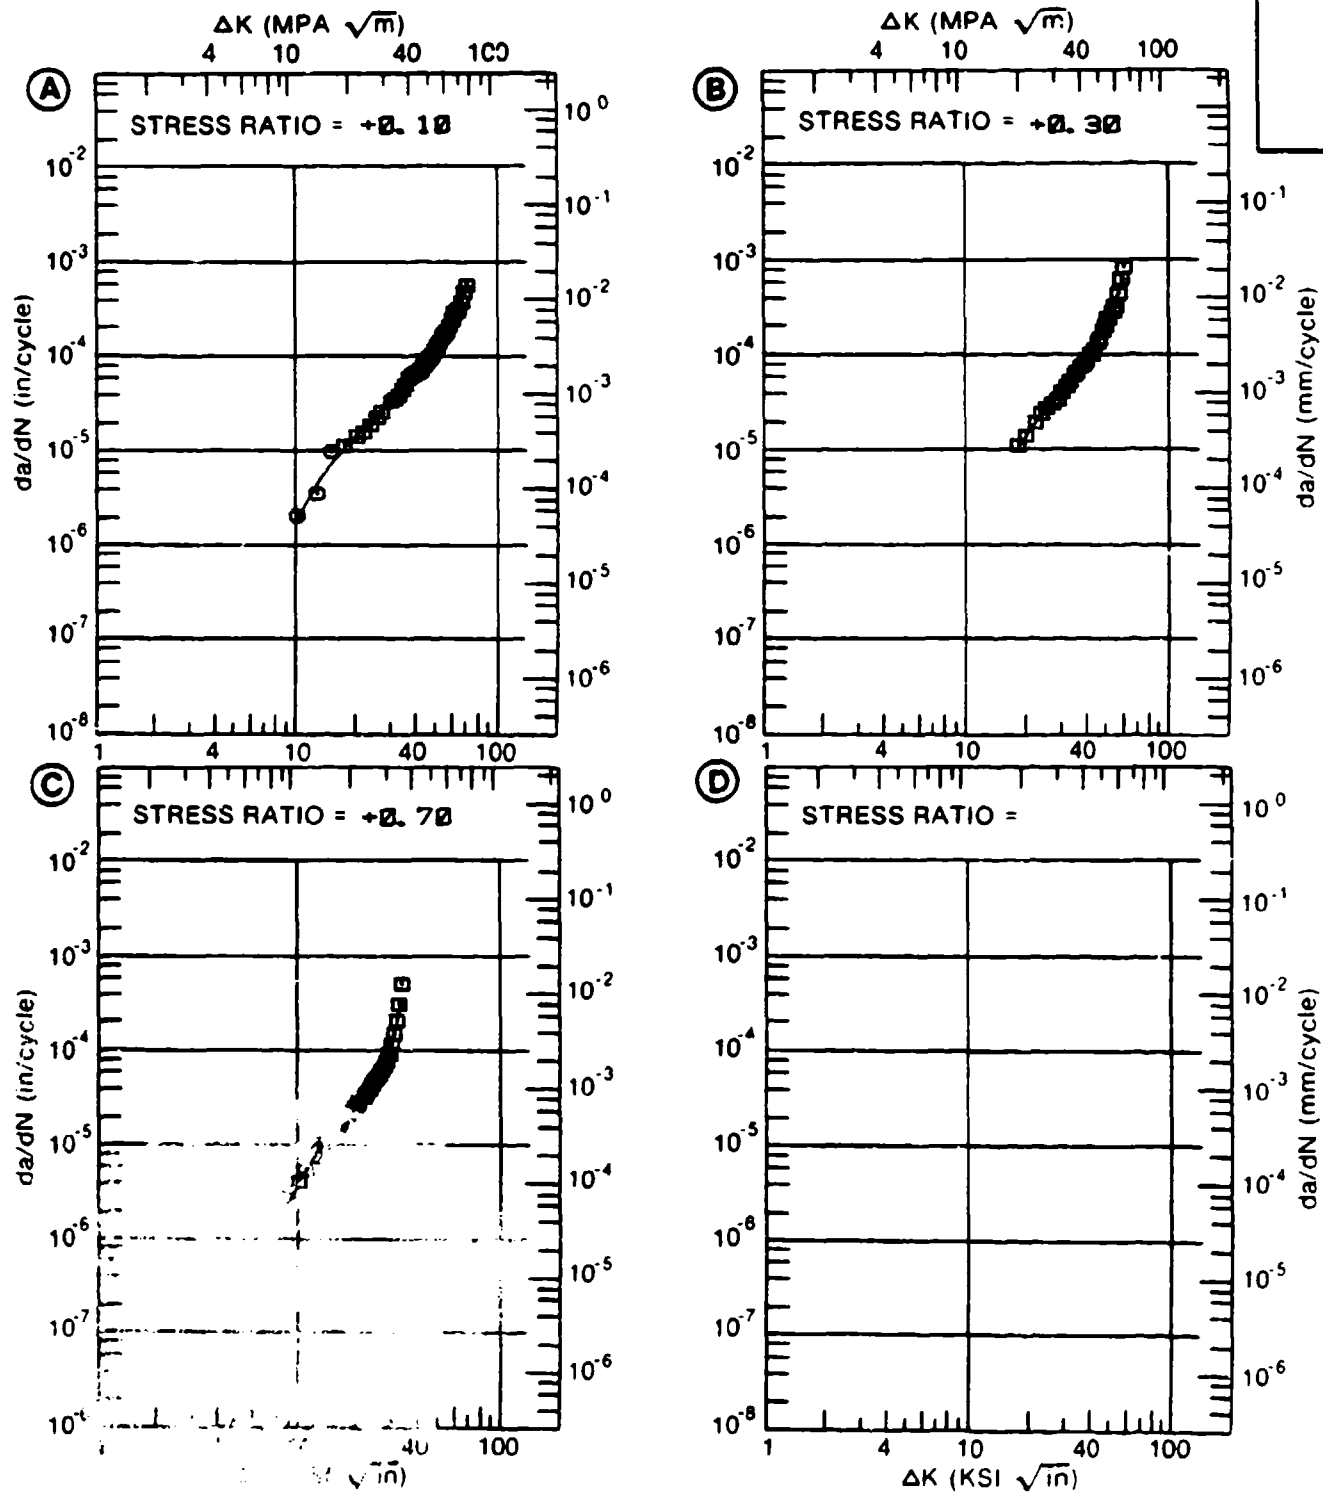


Figure 4.11.3.8

TABLE 4.11.3.9

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.9 INDICATING EFFECT
OF FREQUENCY

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
ENVIRONMENT: R. T. , 3.5% NaCl					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		F(HZ)= 10.00			
DELTA K	A: 9.65	.46			
MIN	B:				
	C:				
	D:				
	10.00	.625			
	13.00	3.62			
	16.00	9.15			
	20.00	17.6			
	25.00	26.5			
	30.00	33.4			
DELTA K	A: 34.71	39.3			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		4.39			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 0.63" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 STRESS RATIO: +0.10
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 124.5 KSI
 ULT. STRENGTH: 136.4 KSI
 SPECIMEN THK: 0.672"
 SPECIMEN WIDTH: 1.500"
 REFERENCES: 90981

TITAN.
 ALLOY

TI-6AL-
 4V

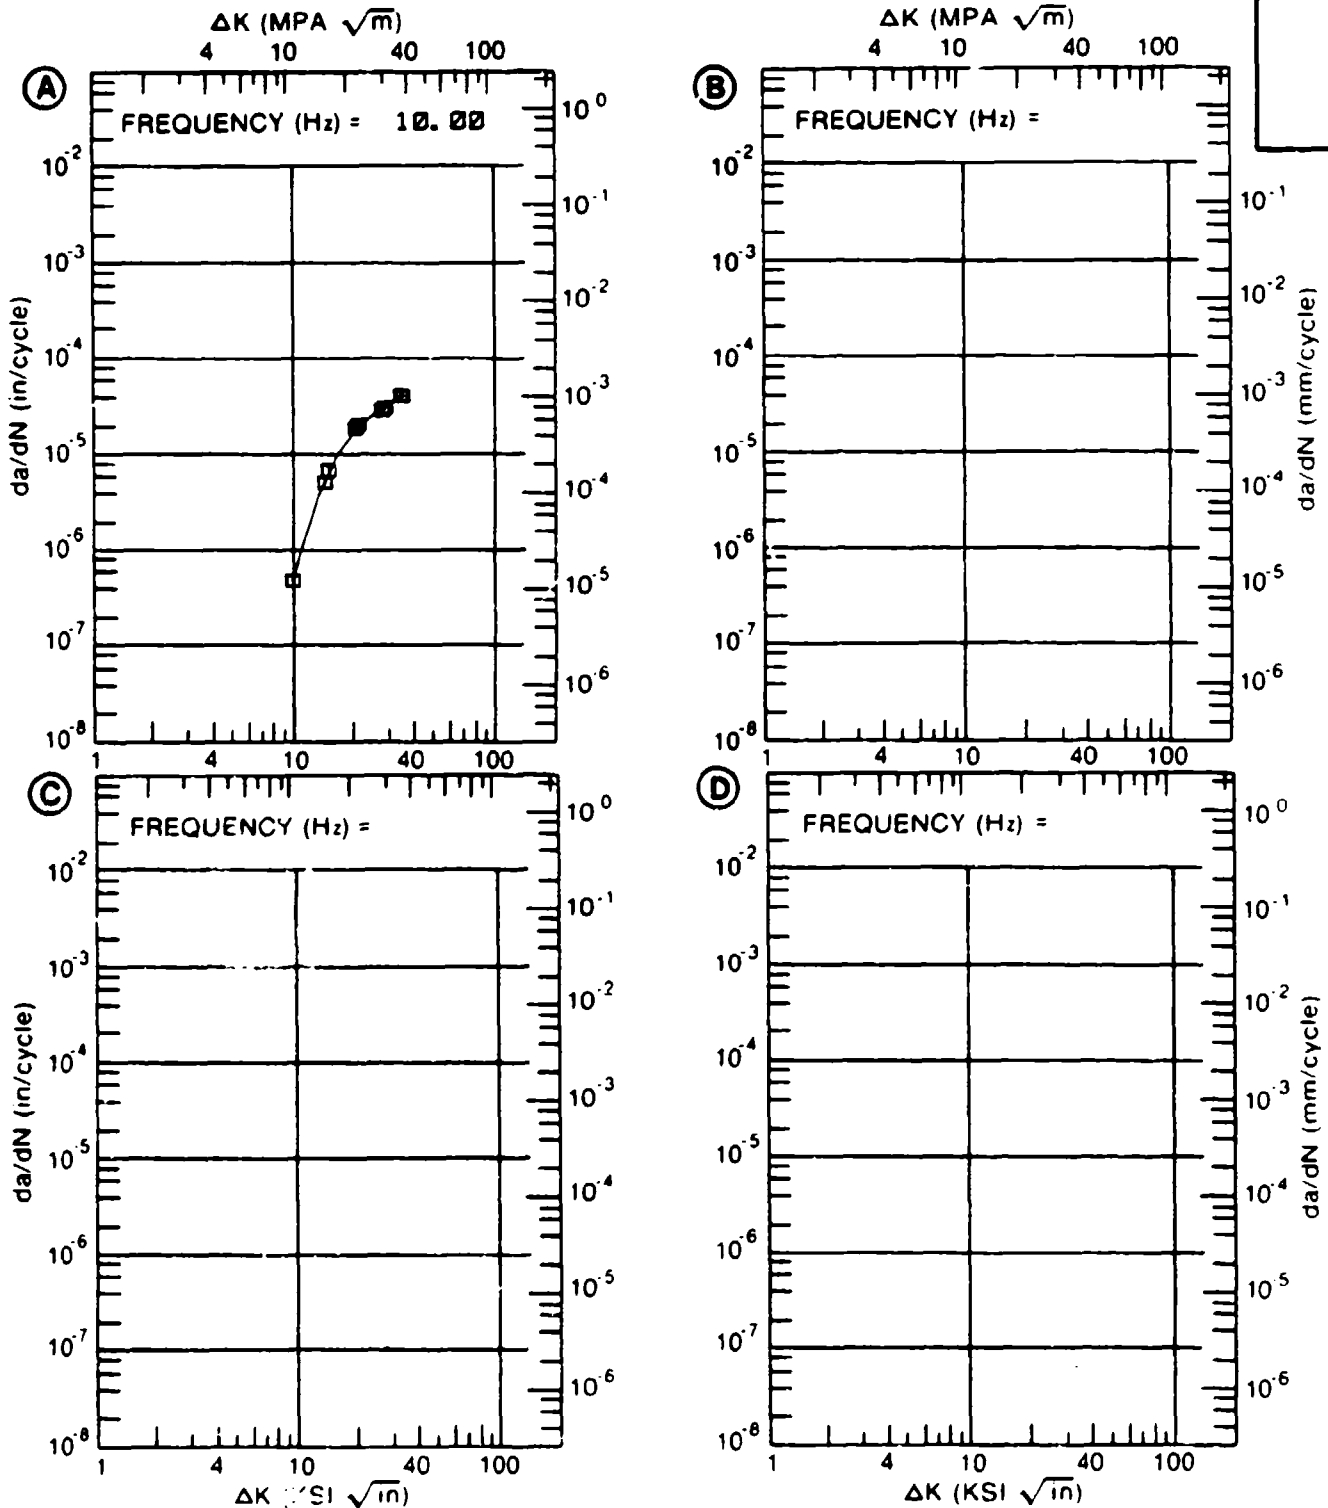


Figure 4.11.3.9

TABLE 4.11.3.10

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.10 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. 3.5%NaCl		
DELTA K MIN	A:				
	B:	8.24	.237		
	C:				
	D:				
	9.00		.574		
	10.00		.985		
	13.00		2.65		
	16.00		6.65		
	20.00		13.8		
	25.00		22.6		
	30.00		31.4		
	35.00		41.7		
	40.00		59.9		
	50.00		109.		
	60.00		245.		
DELTA K MAX	A:				
	B:	68.19	517.		
	C:				
	D:				
ROOT MEAN SQUARE		0.00	18.95		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0		1		
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 0.83" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH: 124.5 KSI
 ULT. STRENGTH: 136.4 KSI
 SPECIMEN THK: 0.660"
 SPECIMEN WIDTH: 2.550- 2.554"
 REFERENCES: 90981

TITAN.
 ALLOY

TI-BAL-
 4V

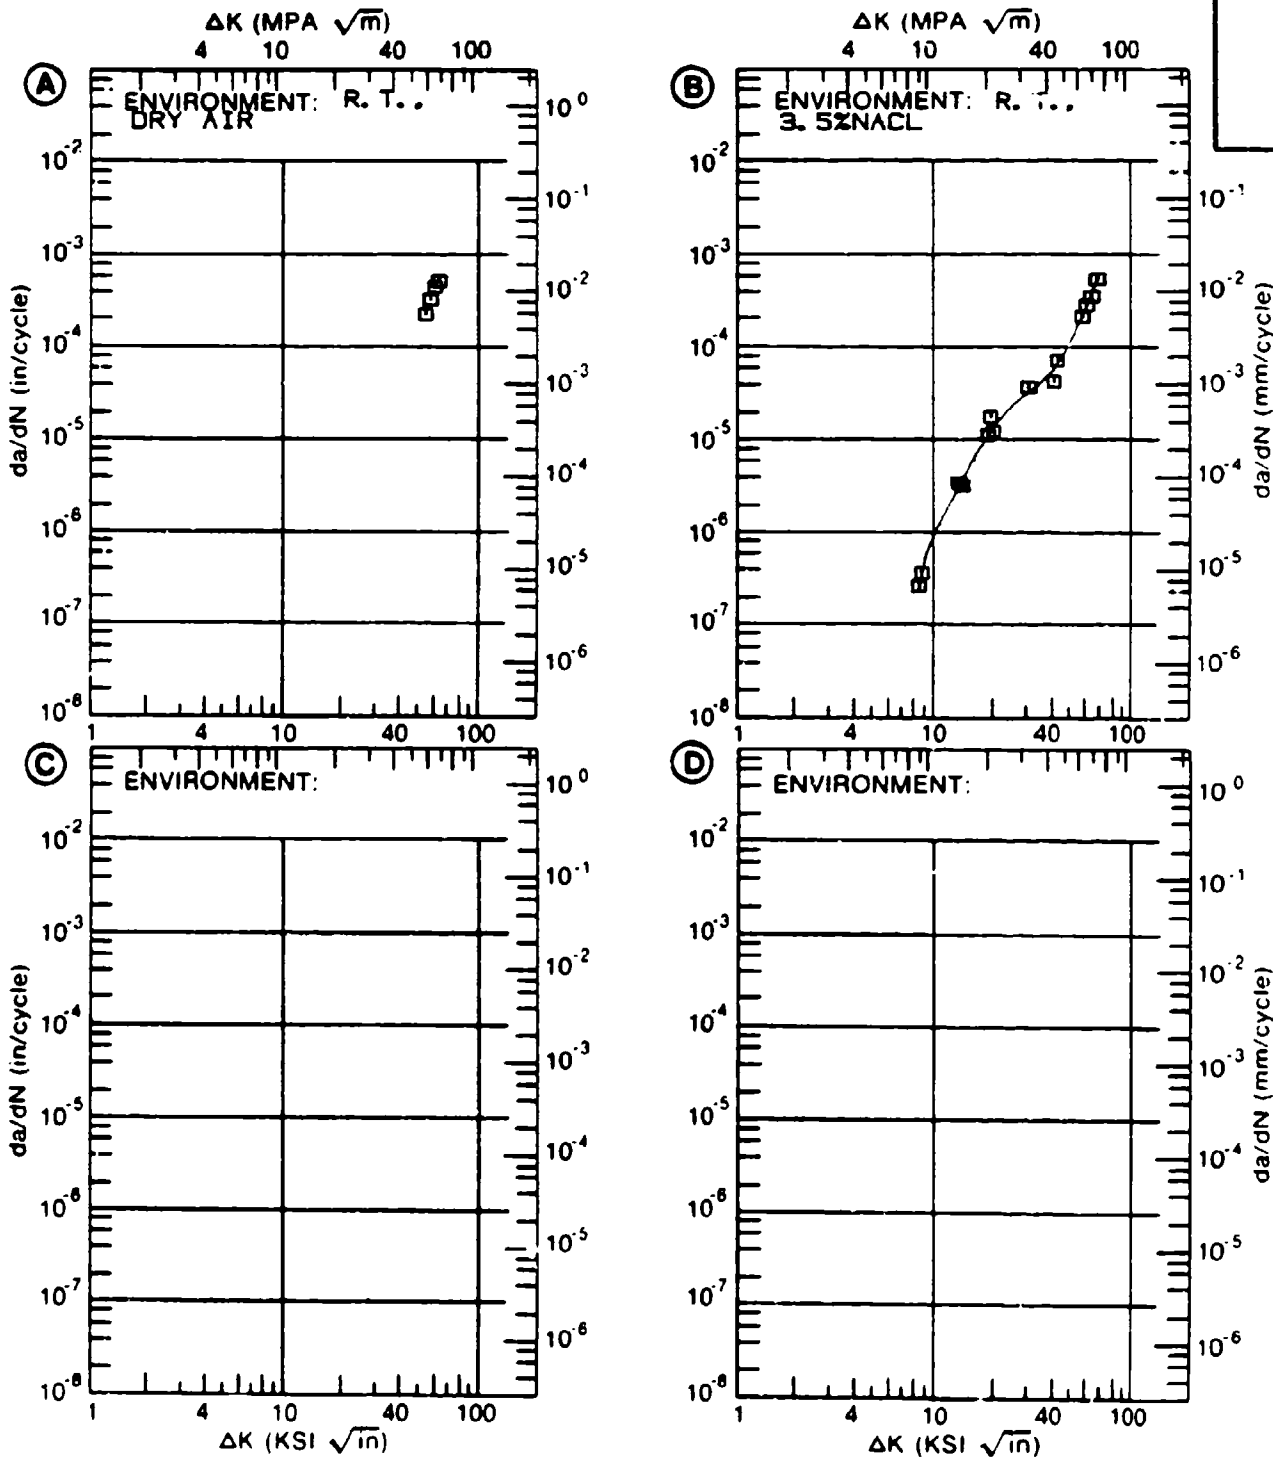


Figure 4.11.3.10

TABLE 4.11.3.11

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.11 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: BA

TI-6AL-4V

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T.			
		S. T. W.			
DELTA K MIN	A: 15.85	11.7			
	B:				
	C:				
	D:				
	16.00	11.9			
	20.00	18.6			
	25.00	28.3			
	30.00	39.2			
	35.00	51.3			
	40.00	64.5			
	50.00	94.3			
	60.00	129.			
	70.00	168.			
	80.00	213.			
DELTA K MAX	A: 87.57	252.			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 10.42
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: BA
 FORM: 0.63" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH: 124.5 KSI
 ULT. STRENGTH: 136.4 KSI
 SPECIMEN THK: 0.660"
 SPECIMEN WIDTH: 2.554"
 REFERENCES: 90981

TITAN.
 ALLOY
 TI-6AL-
 4V

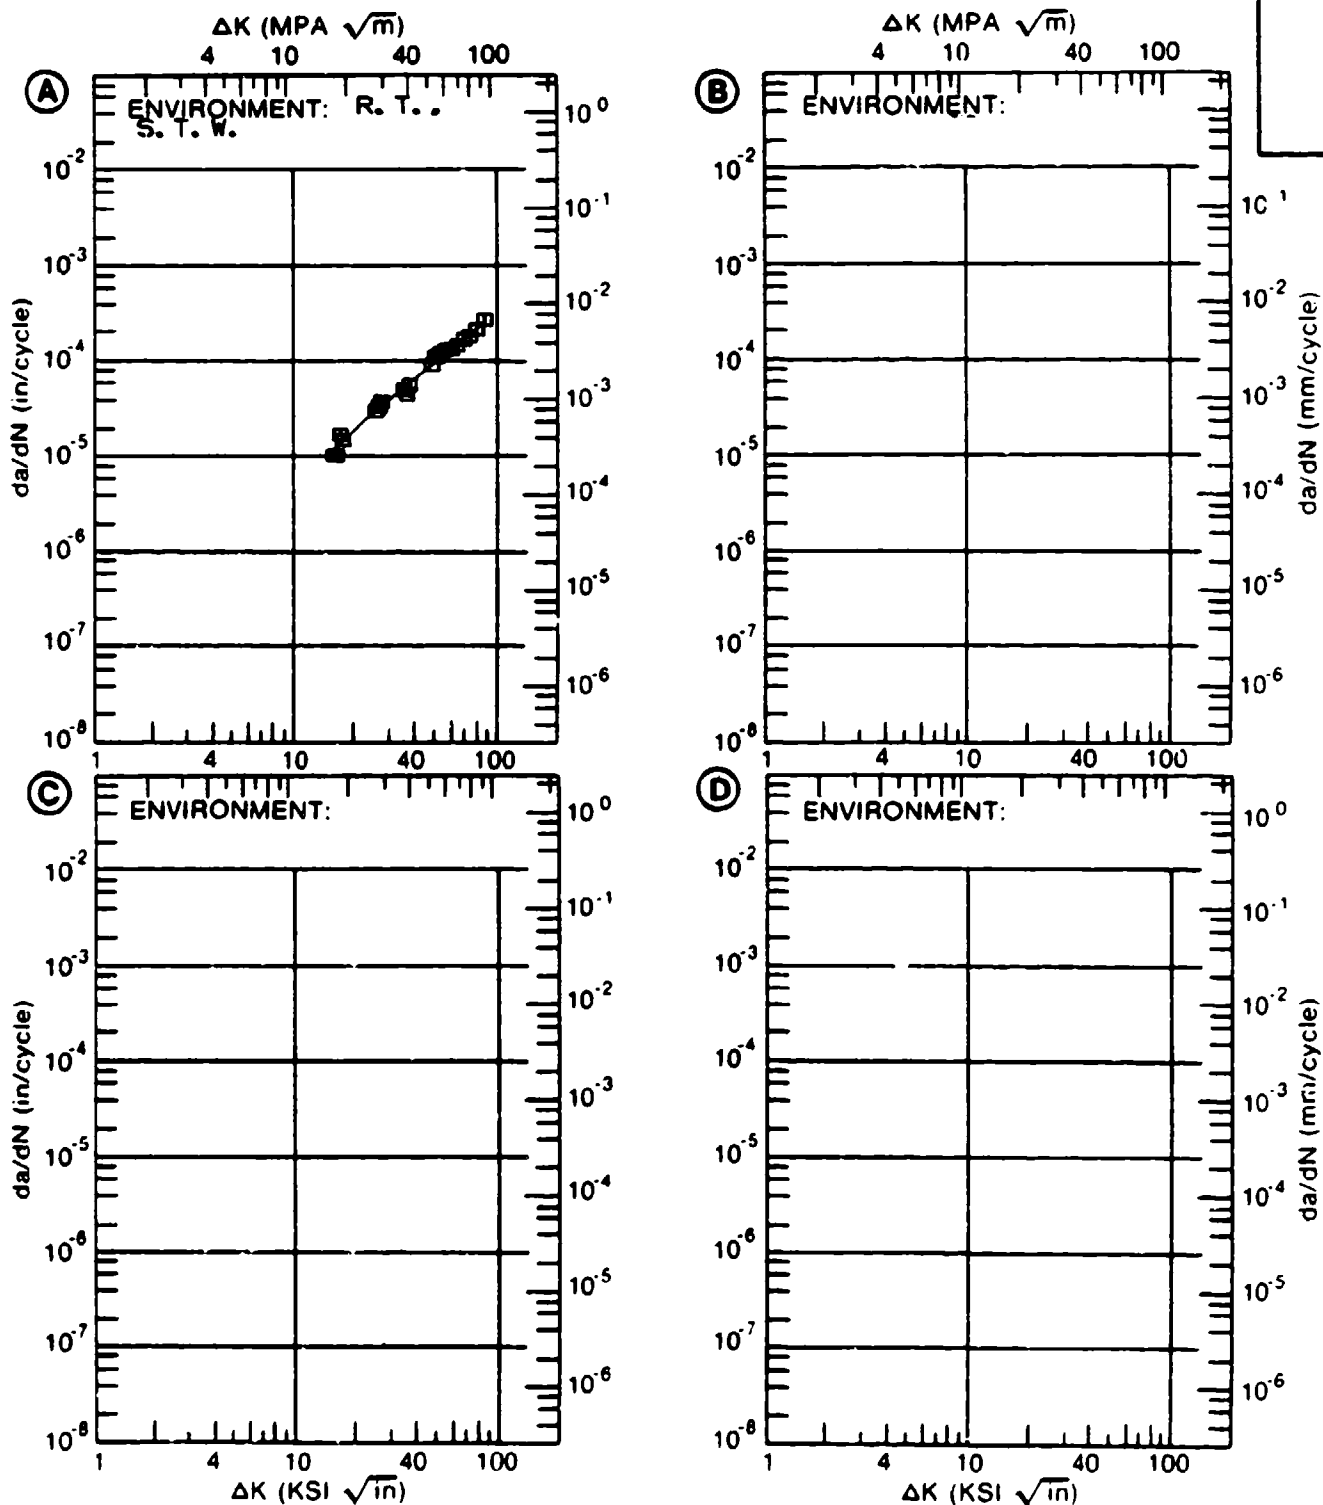


Figure 4.11.3.11

TABLE 4.11.3.12

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.12 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T.		E= R. T.	
		3.5%NaCl		S. T. W.	
DELTA K MIN	A: 10.21	.250			
	B: 18.51		30.5		
	C:				
	D:				
	13.00	5.35			
	16.00	16.0			
	20.00	38.5	35.3		
	25.00	66.4	73.3		
	30.00	83.1	95.4		
	35.00	100.	103.		
	40.00	136.	112.		
	50.00	281.	192.		
	60.00		489.		
DELTA K MAX	A: 57.34	342.			
	B: 69.64		1087.		
	C:				
	D:				
ROOT MEAN SQUARE		17.39	15.35		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0		1		

CONDITION/HT: BA
 FORM: 0.63" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 124.5 KSI
 ULT. STRENGTH: 136.4 KSI
 SPECIMEN THK: 0.660"
 SPECIMEN WIDTH: 2.550- 2.554"
 REFERENCES: 90981

TITAN.
 ALLOY

TI-6AL--
 4V

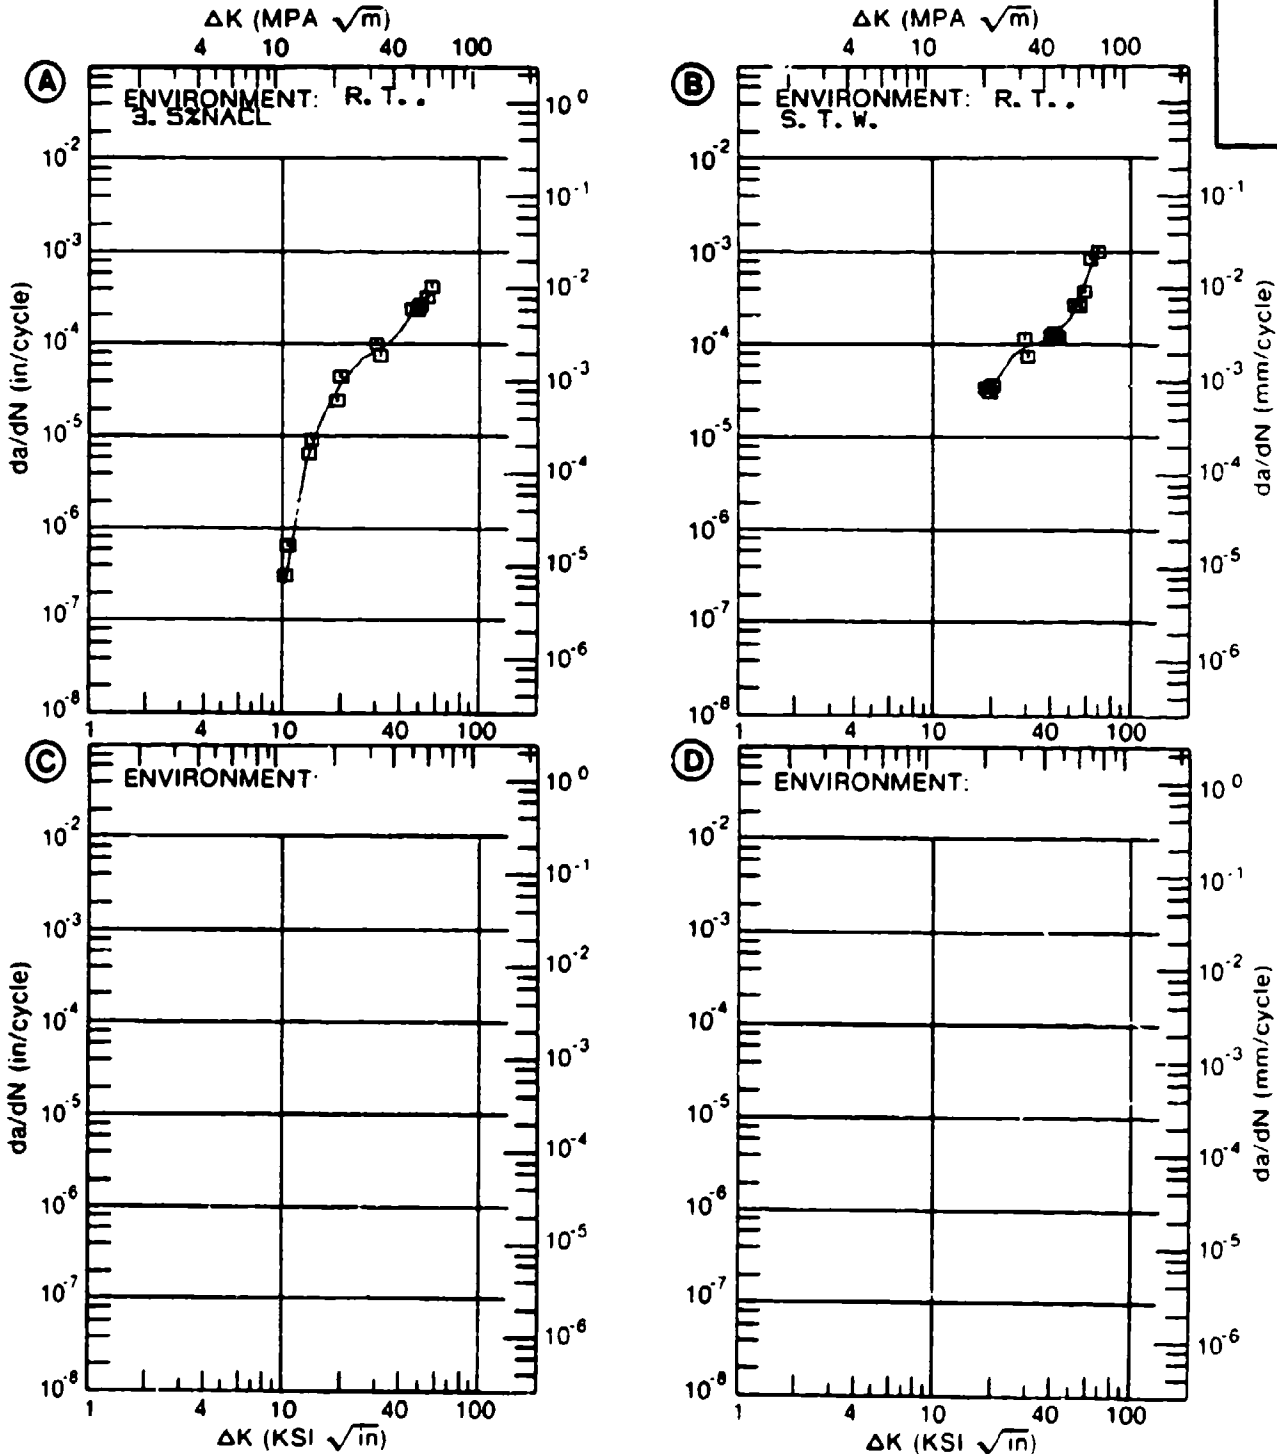


Figure 4.11.3.12

TABLE 4.11.3.13

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.13 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: BA

TI-6AL-4V

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. S. T. W.			
DELTA K	A: 9.81	.55			
MIN	B:				
	C:				
	D:				
	10.00	.581			
	13.00	1.31			
	16.00	2.73			
	20.00	6.43			
	25.00	16.2			
	30.00	36.1			
	35.00	72.9			
	40.00	136.			
	50.00	400.			
	60.00	987.			
DELTA K	A: 69.91	2127.			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 43.57
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0 1
(NP/NA) >2.0

CONDITION/HT: BA
 FORM: 0.83" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 0.10 HZ

YIELD STRENGTH: 124.5 KSI
 ULT. STRENGTH: 136.4 KSI
 SPECIMEN THK: 0.860"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: 90981

TITAN.
 ALLOY

TI-6AL-
 4V

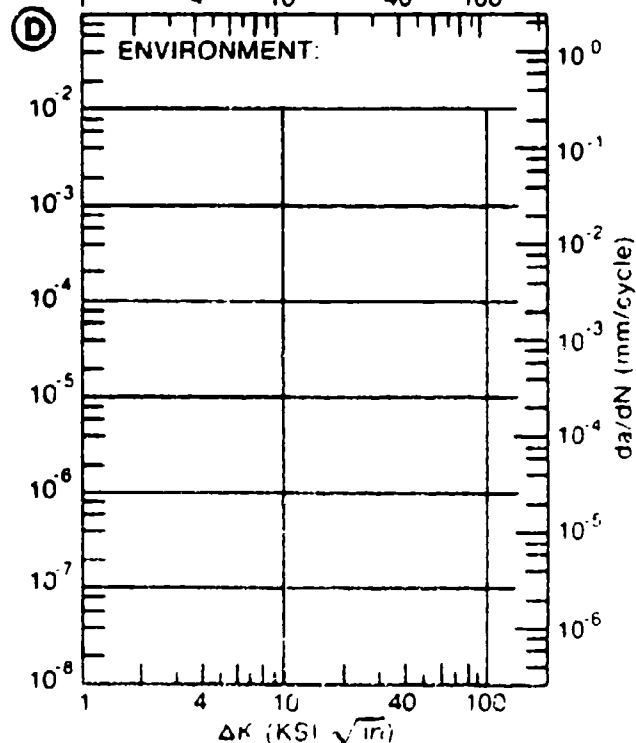
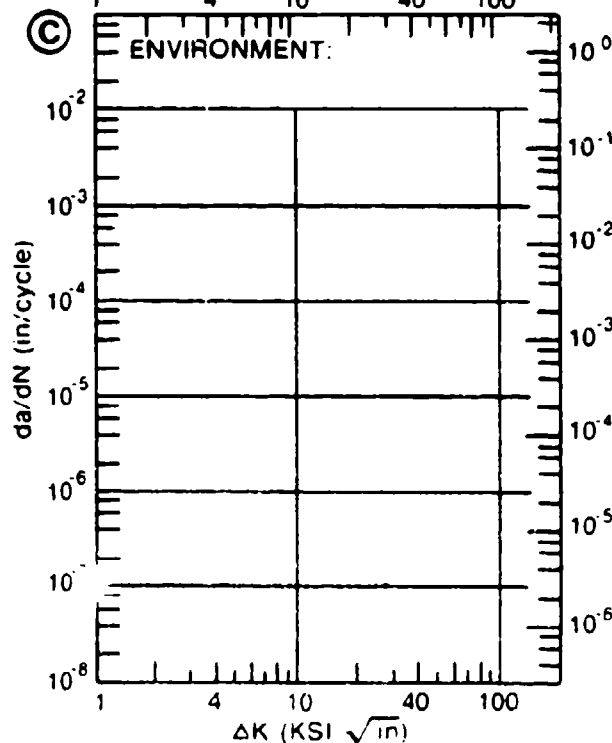
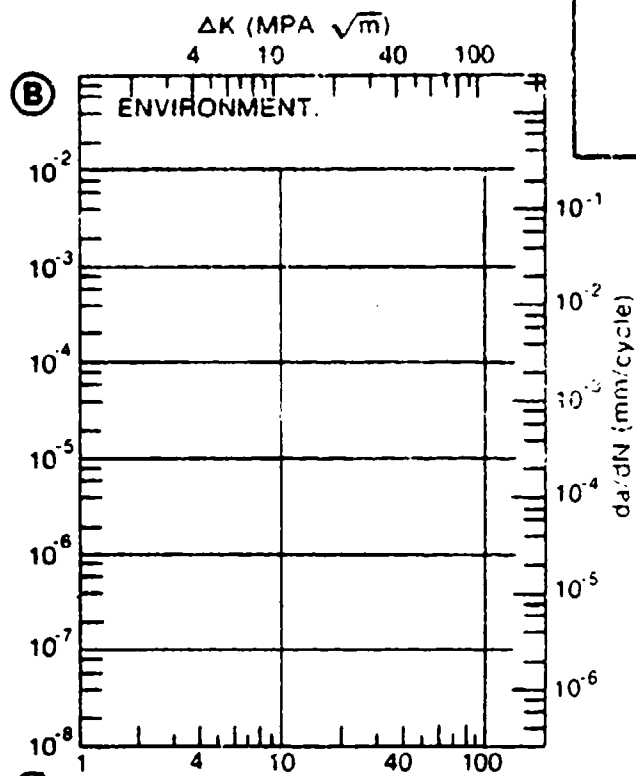
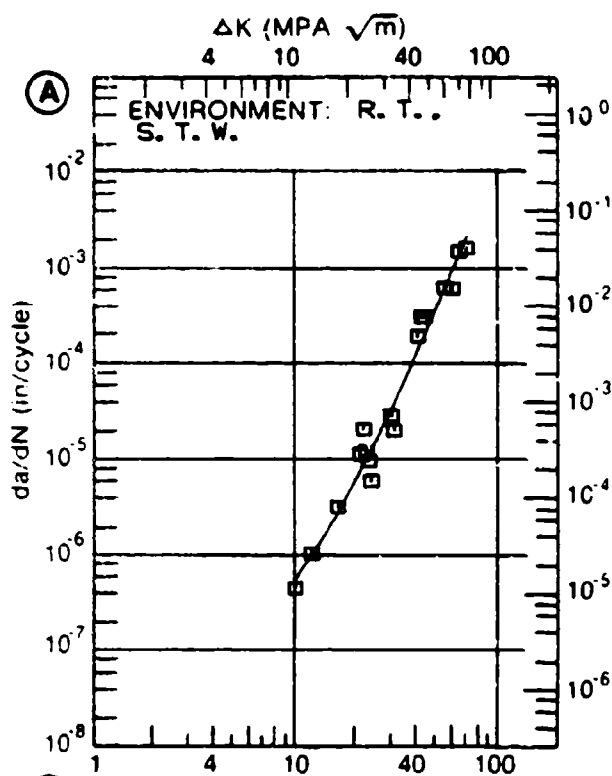


Figure 4.11.3.13

TABLE 4.11.3.14

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.14 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
ENVIRONMENT: R. T. , DRY AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.30		
DELTA K	A: 7.64	.108			
MIN	B: 9.89		.284		
	C:				
	D:				
	8.00	.113			
	9.00	.150			
	10.00	.227	.302		
	13.00	.937	1.79		
	16.00	3.17	4.90		
	20.00	9.17	9.75		
	25.00	19.6	18.5		
	30.00	33.0	32.2		
	35.00	51.5	52.4		
	40.00	78.0			
DELTA K	A: 45.52	122.			
MAX	B: 39.92		80.2		
	C:				
	D:				
ROOT MEAN SQUARE		16.21	10.73		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25		1		
SUMMARY	1.25-2.0	1			
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 0.78" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., DRY AIR

YIELD STRENGTH: 116.3 KSI
 ULT. STRENGTH: 125.7 KSI
 SPECIMEN THK: 0.747- 0.748"
 SPECIMEN WIDTH: 4.995- 5.008"
 REFERENCES 98575

TITAN.
 ALLOY

TI-6AL-
 4V

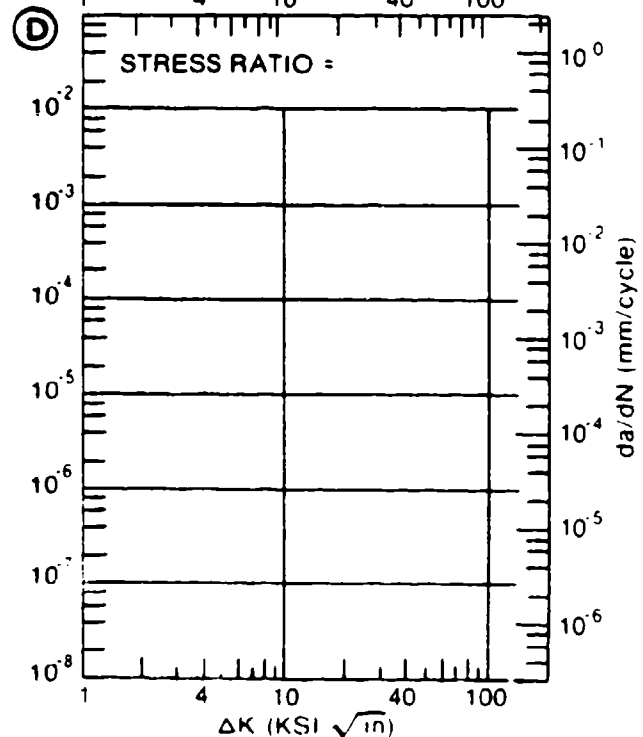
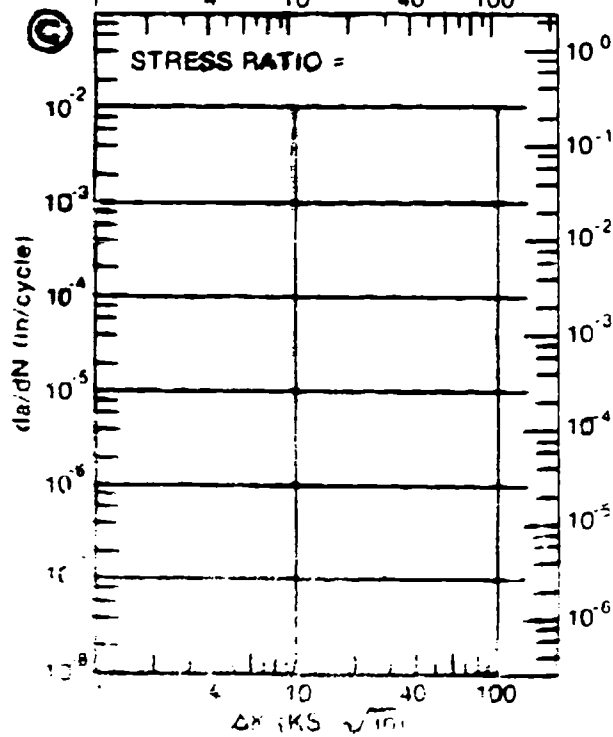
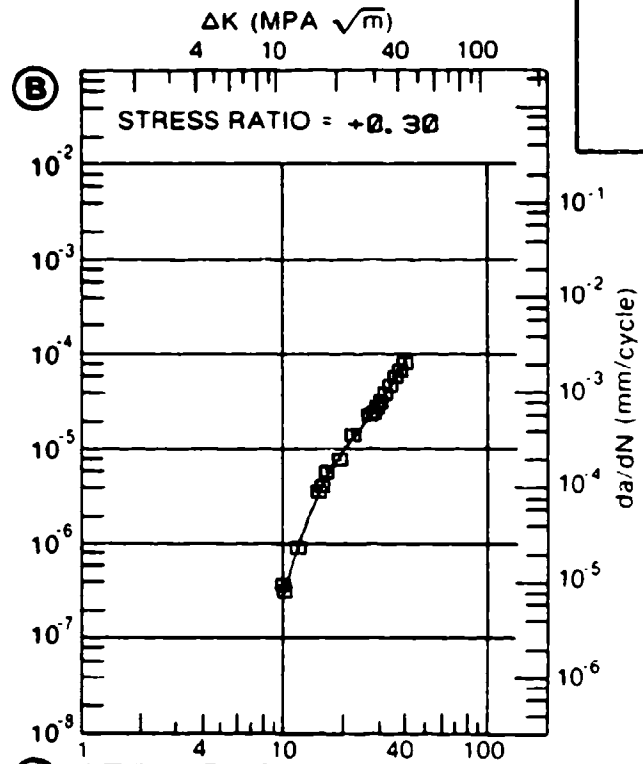
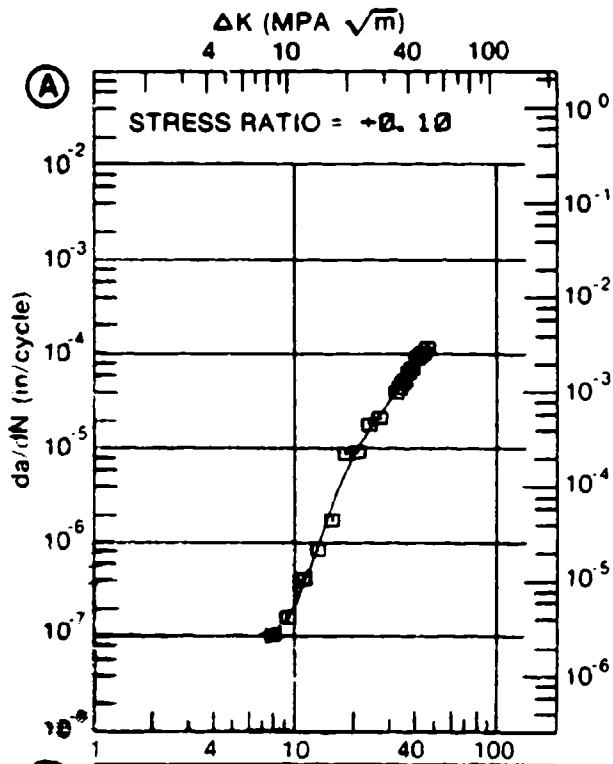


Figure 4.11.3.14

TABLE 4.11.3.15

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.15 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
ENVIRONMENT: R. T. , S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K A:	11.43	.30			
DELTA K B:	24.08		53.3		
MIN C:					
D:					
	13.00	.730			
	16.00	3.08			
	20.00	11.1			
	25.00	27.6	61.5		
	30.00	48.0	86.0		
	35.00	70.5	119.		
	40.00	95.9			
	50.00	163.			
DELTA K A:	59.09	264.			
DELTA K B:	36.06		134.		
MAX C:					
D:					
ROOT MEAN SQUARE		16.76	3.81		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25		1		
SUMMARY	1.25-2.0	2			
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 0.75- 0.76" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 116.3 KSI
 ULT. STRENGTH: 125.7 KSI
 SPECIMEN THK: 0.746- 0.751"
 SPECIMEN WIDTH: 4.986- 5.019"
 REFERENCES: 89575

TITAN.
 ALLOY
 TI-6AL-
 4V

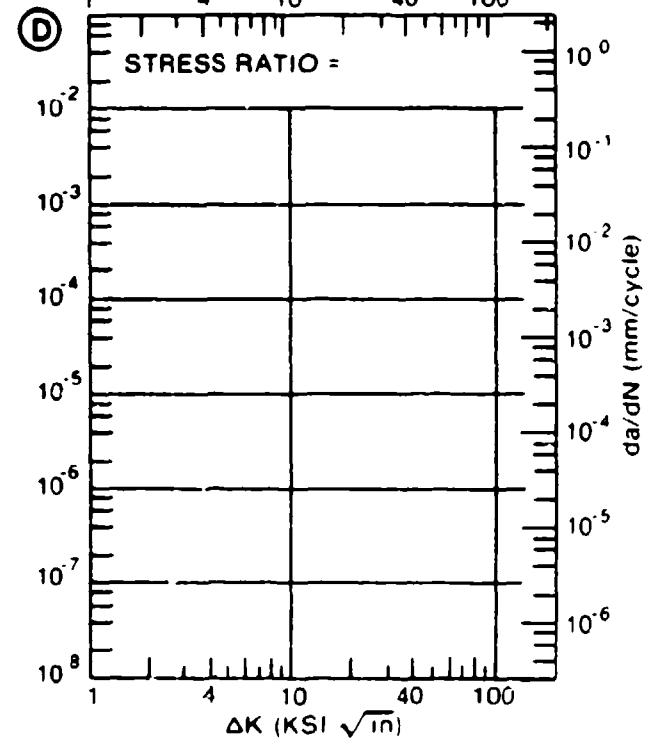
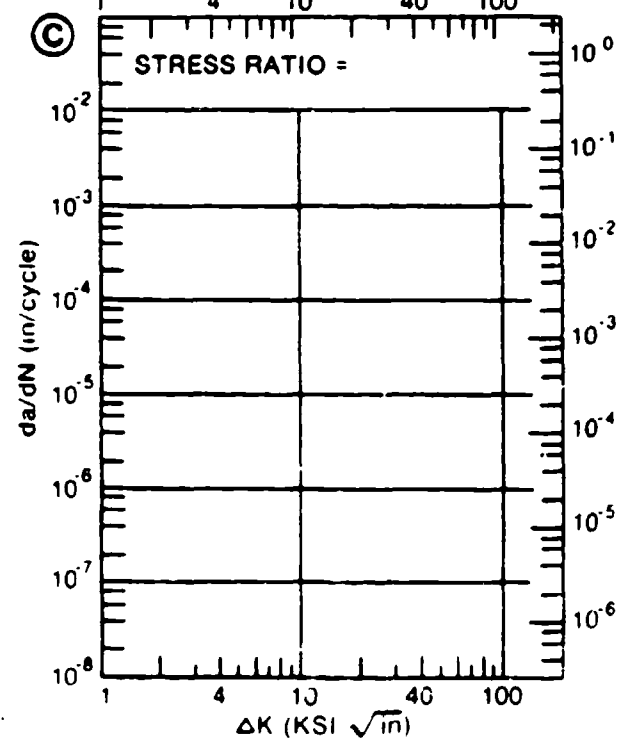
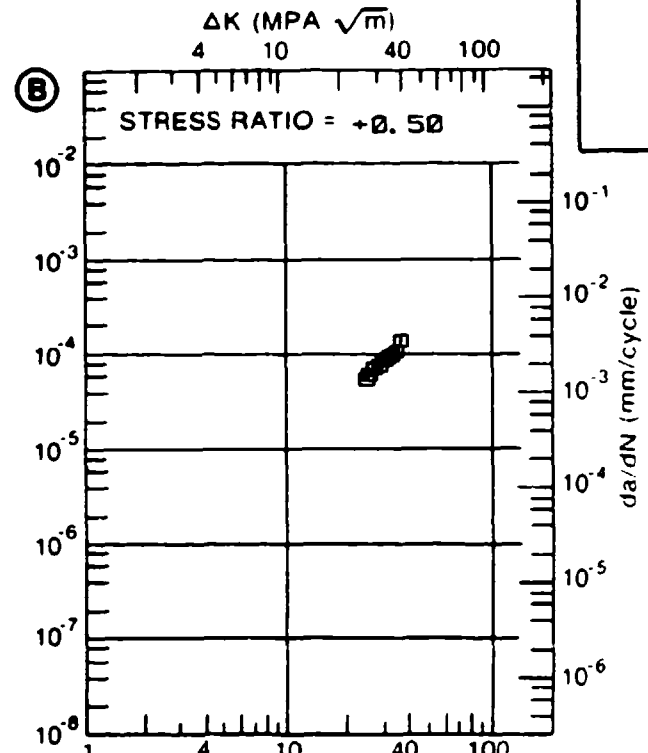
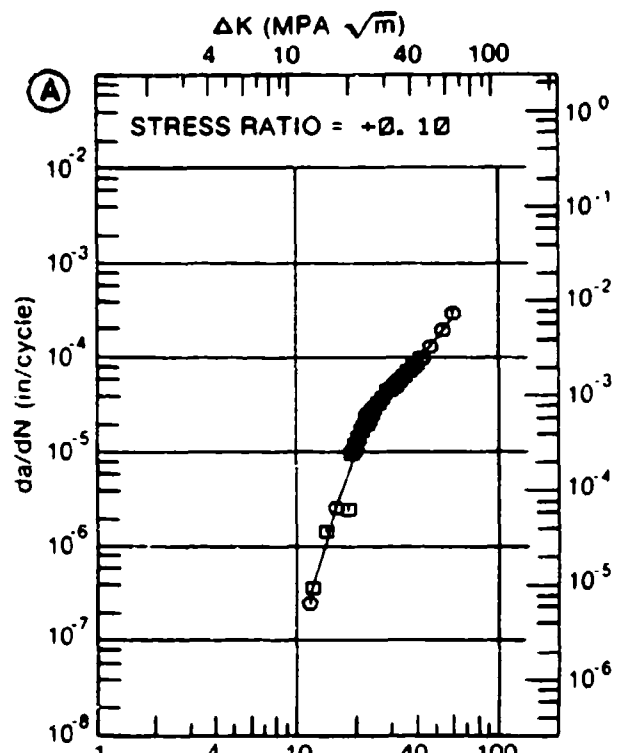


Figure 4.11.3.15

TABLE 4.11.3.16

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.16 INDICATING EFFECT
OF FREQUENCY

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: BA
ENVIRONMENT: R. T. , S. T. W.

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	F (HZ) = 0.10			
DELTA K A:				
MIN B:				
C:				
D:				
200.00				
DELTA K A:				
MAX B:				
C:				
D:				

ROOT MEAN SQUARE 0.00
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: BA
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.50
 ENVIRONMENT: R. T. . S. T. W.

YIELD STRENGTH: 116.3 KSI
 ULT. STRENGTH: 125.7 KSI
 SPECIMEN THK: 0.750"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 88575

TITAN.
 ALLOY

TI-6AL-4V

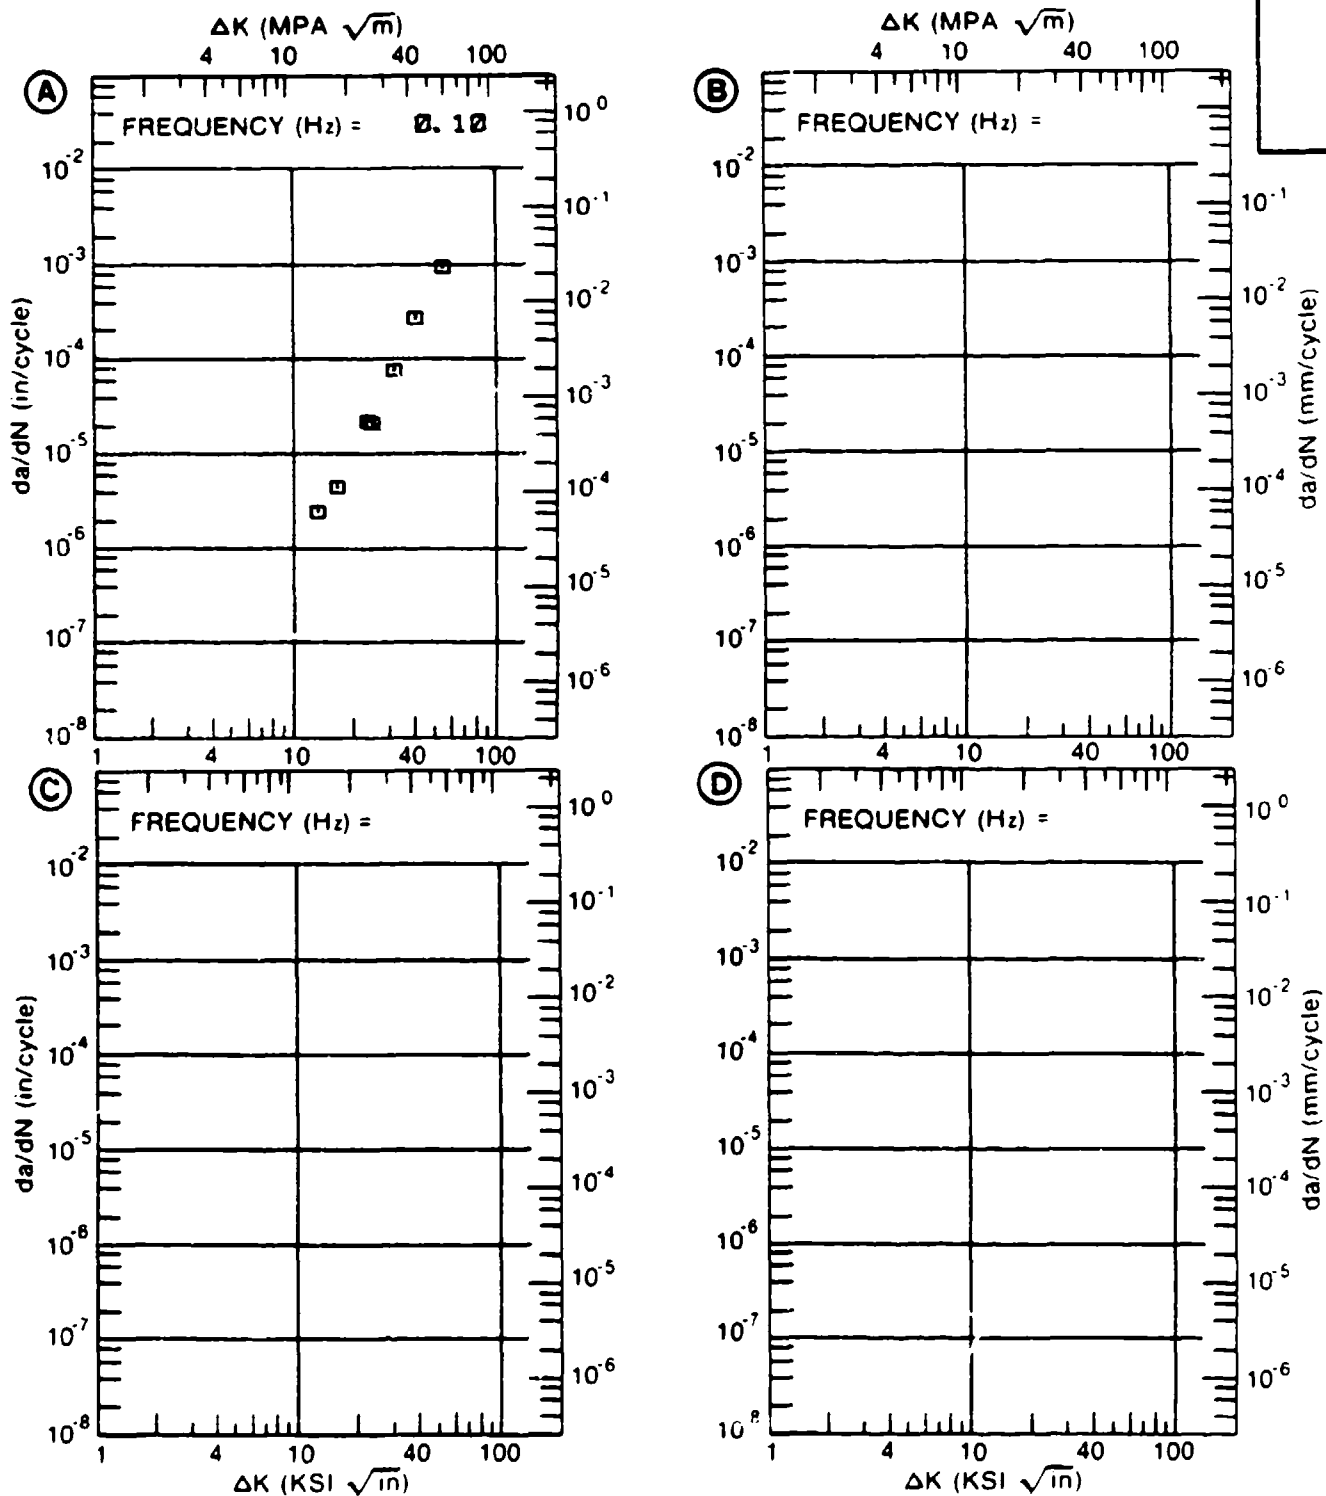


Figure 4.11.3.16

TABLE 4.11.3.17

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.17 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
ENVIRONMENT: R. T. , DIST. WATER					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 50		
DELTA K A:	26. 53	15. 5			
MIN B:					
C:					
D:					
	30. 00	26. 2			
	35. 00	45. 2			
	40. 00	67. 8			
	50. 00	126.			
	60. 00	218.			
DELTA K A:	63. 96	271.			
B:					
MAX C:					
D:					
ROOT MEAN SQUARE		3. 71	0. 00		
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25				
SUMMARY	1. 25-2. 0				
(NP/NA)	>2. 0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 FREQUENCY: 0.10 HZ
 ENVIRONMENT: R.T., DIST. WATER

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 00140

TITAN.
 ALLOY

TI-6AL-
 4V

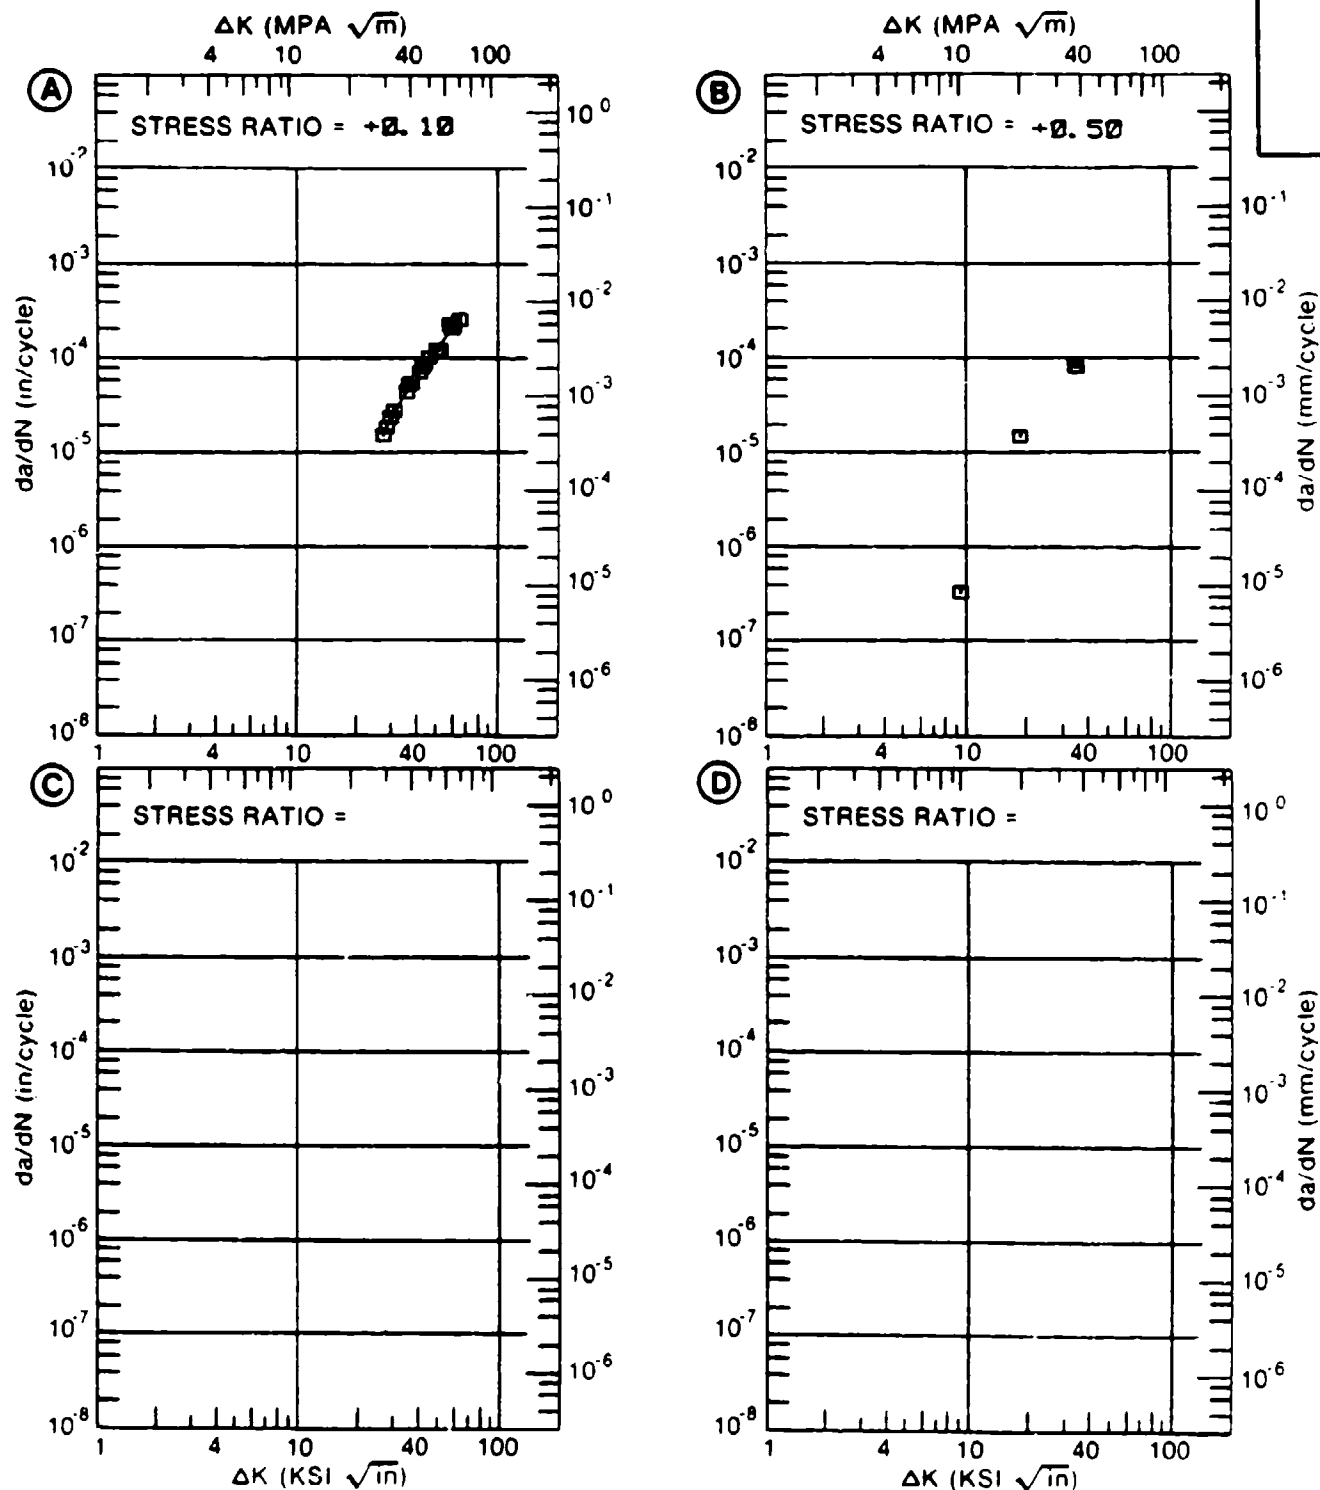


Figure 4.11.3.17

TABLE 4.11.3.18

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.11.3.18 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 30	R=+0. 50	
DELTA K	A: 12.84	.965			
MIN	B: 10.82		.451		
	C: 10.92			1.47	
	D:				
	13.00	.929	1.15	1.62	
	16.00	1.19	3.13	3.85	
	20.00	4.10	9.31	12.0	
	25.00	12.4	23.5	27.6	
	30.00	25.3	38.6	44.0	
	35.00	41.9	52.8	78.0	
	40.00	62.0	84.8	182.	
	50.00	115.		1010.	
	60.00	208.			
DELTA K	A: 66.20	454.			
MAX	B: 48.80		210.		
	C: 50.10			1013.	
	D:				
ROOT MEAN SQUARE		15.43	11.45	16.49	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1		1	
SUMMARY	1.25-2.0		1		
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 2.25" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 0.10 HZ
 ENVIRONMENT: R. T. . H. H. A.

YIELD STRENGTH: 117.0 KSI
 ULT. STRENGTH: 129.4 KSI
 SPECIMEN THK: 0.749- 0.753"
 SPECIMEN WIDTH: 5.009- 5.013"
 REFERENCES: G007

TITAN.
 ALLOY

TI-6AL-
 4V

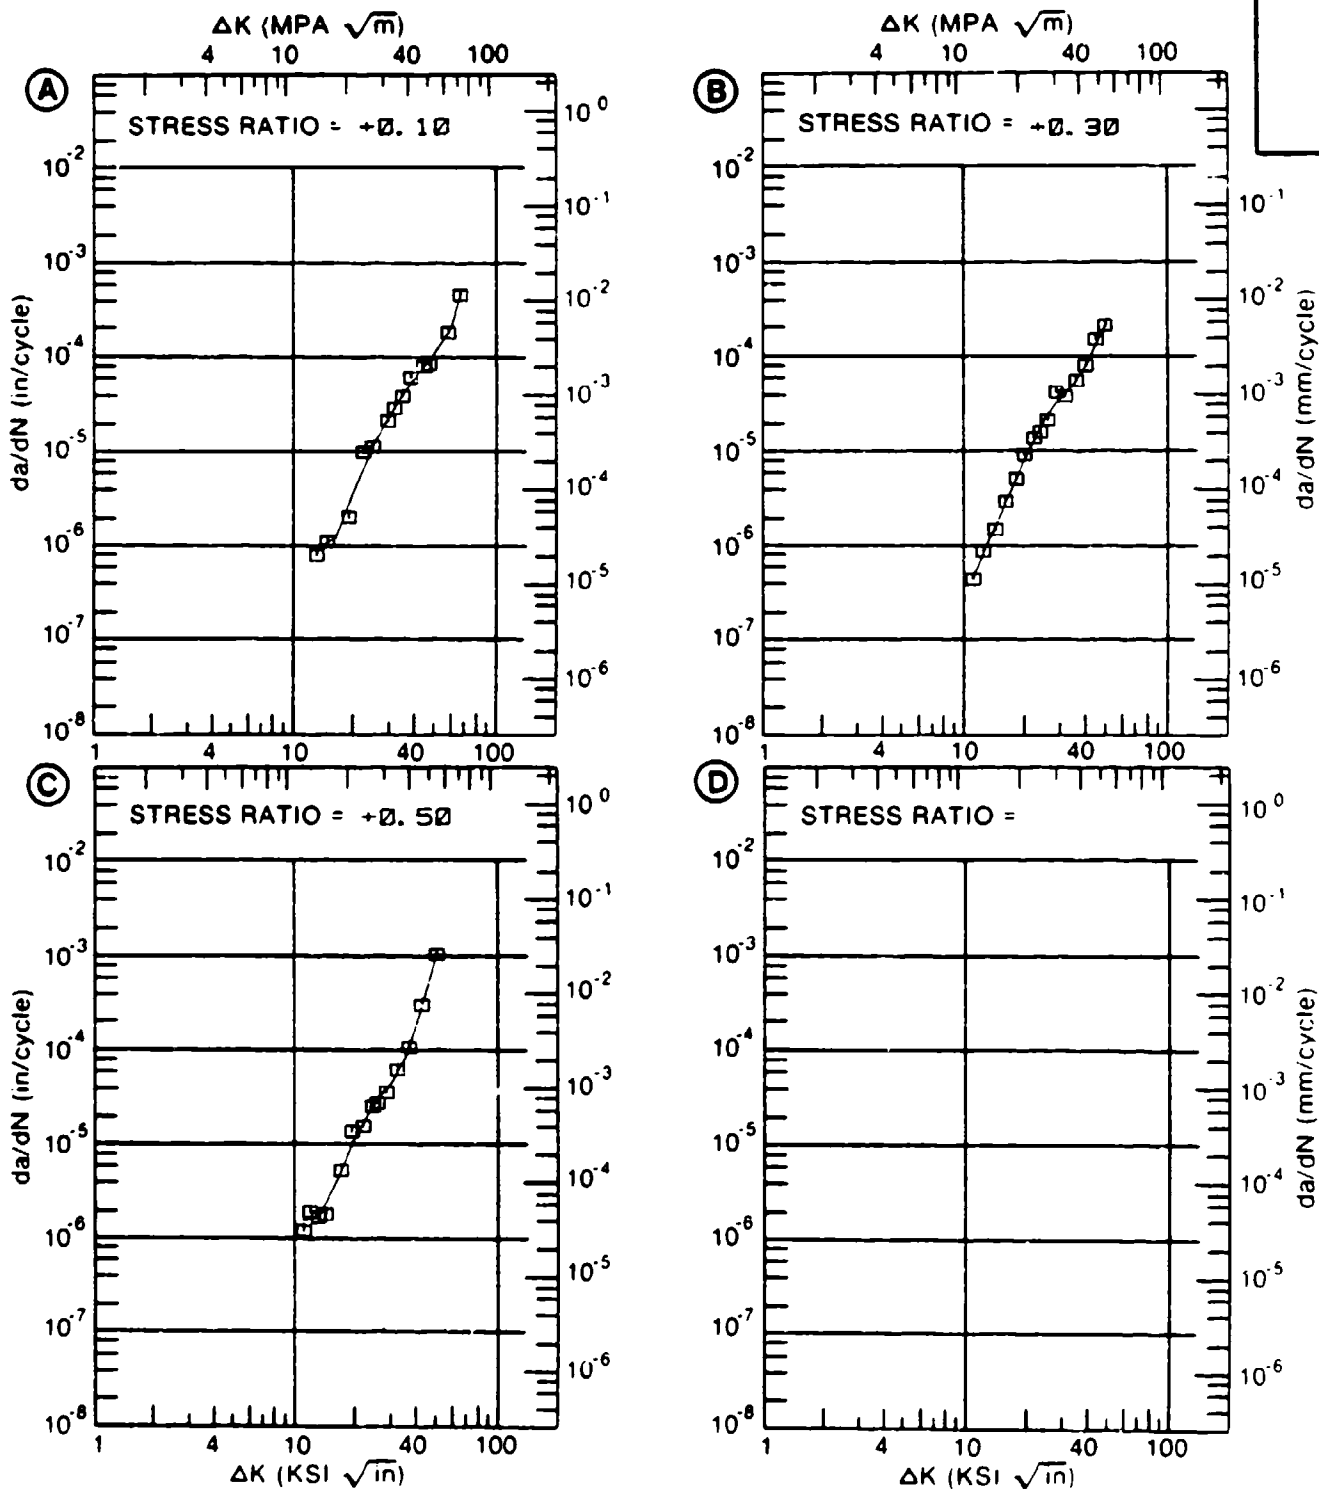


Figure 4.11.3.18

TABLE 4.11.3.19

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.19 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: BA
ENVIRONMENT: R. T. , DRY AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
A:	9.56	.04			
B:	7.43		.40		
C:					
D:					
	8.00		.538		
	9.00		.826		
	10.00	.0692	1.19		
	13.00	.482	2.85		
	16.00	1.62	5.49		
	20.00	5.42	10.9		
	25.00	15.7	21.5		
	30.00	32.2	38.1		
	35.00	51.7	62.5		
	40.00	69.3			
	50.00	85.6			
A:	50.68	85.7			
B:	36.97		74.9		
C:					
D:					

ROOT MEAN SQUARE 22.63 47.03
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0 1 1
(NP/NA) >2.0

CONDITION/HT: BA
 FORM: 2.79" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., DRY AIR

YIELD STRENGTH: 116.3 KSI
 ULT. STRENGTH: 125.7 KSI
 SPECIMEN THK: 0.760- 0.762"
 SPECIMEN WIDTH: 4.993- 4.996"
 REFERENCES: 88575

TITAN.
 ALLOY
 TI-6AL-
 4V

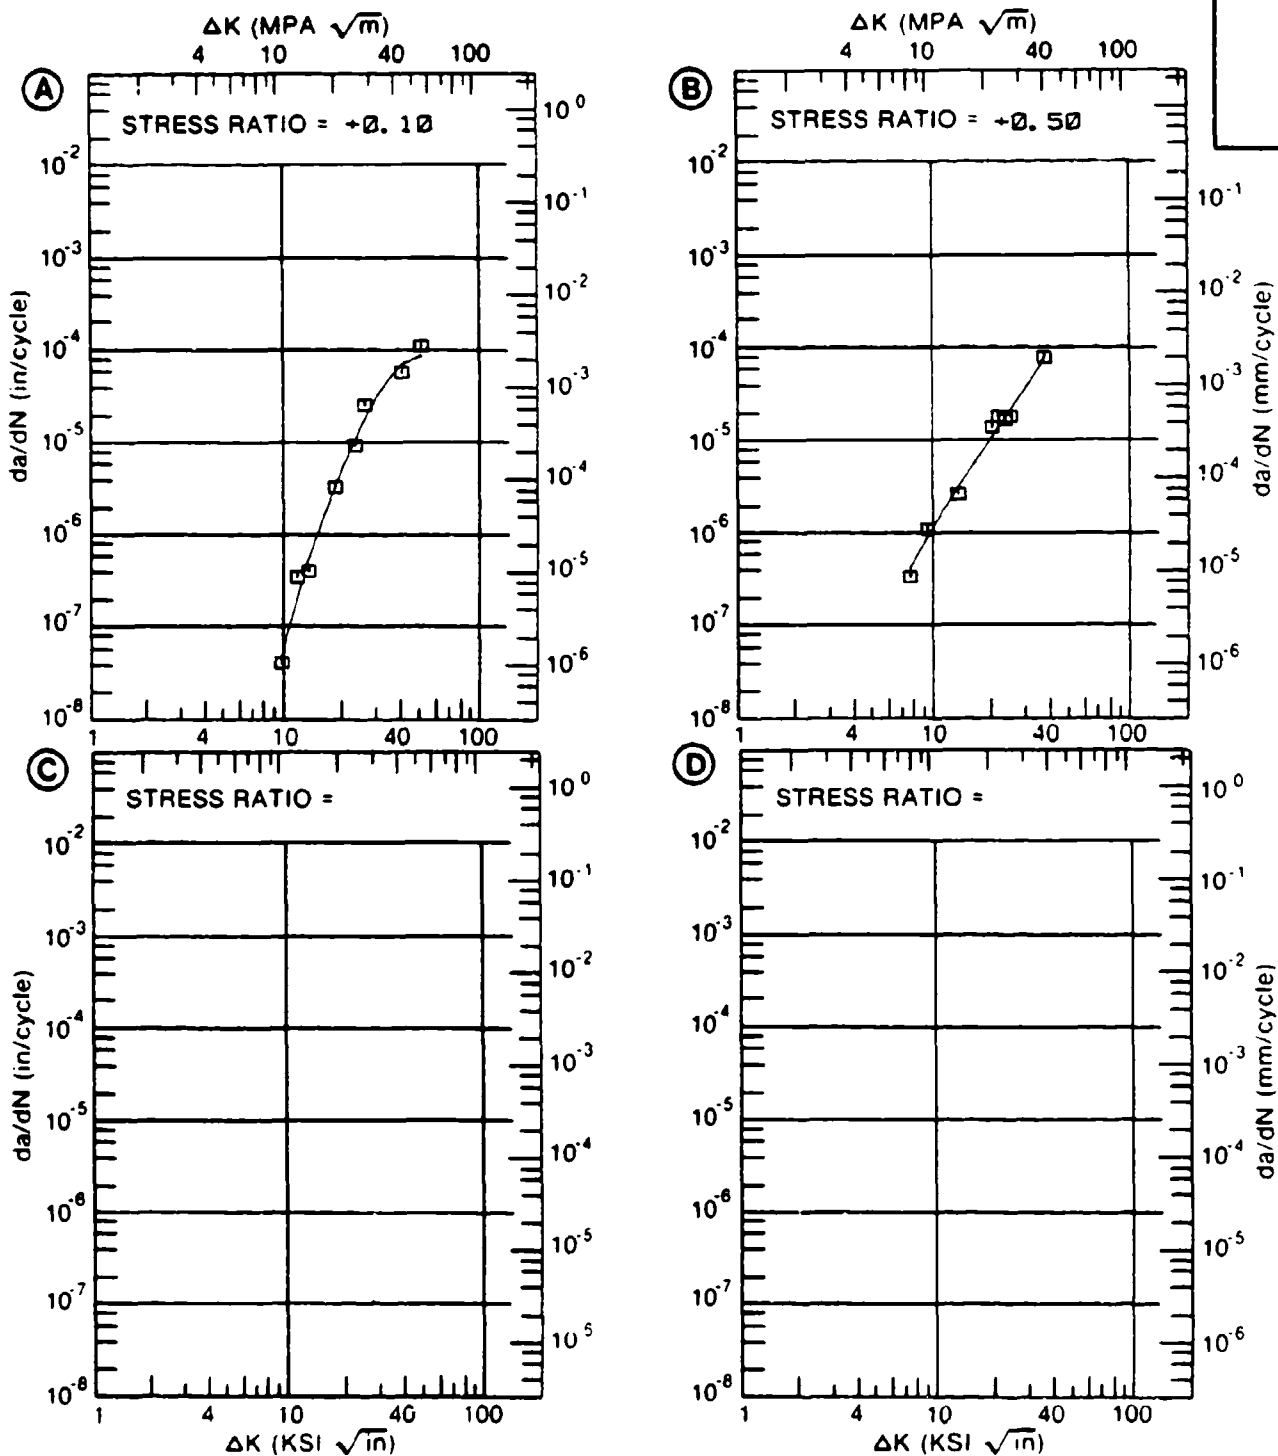


Figure 4.11.3.19

TABLE 4.11.3.20

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.20 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T.			
		S. T. W.			
DELTA K MIN	A: B: C: D:				
200.00					
DELTA K MAX	A: B: C: D:				
ROOT MEAN SQUARE		0.00			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 2.79" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: S-L
 STRESS RATIO: +0.10
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 116.3 KSI
 ULT. STRENGTH: 125.7 KSI
 SPECIMEN THK: 1.002"
 SPECIMEN WIDTH: 1.996"
 REFERENCES: 88575

TITAN.
 ALLOY

TI-6AL-4V

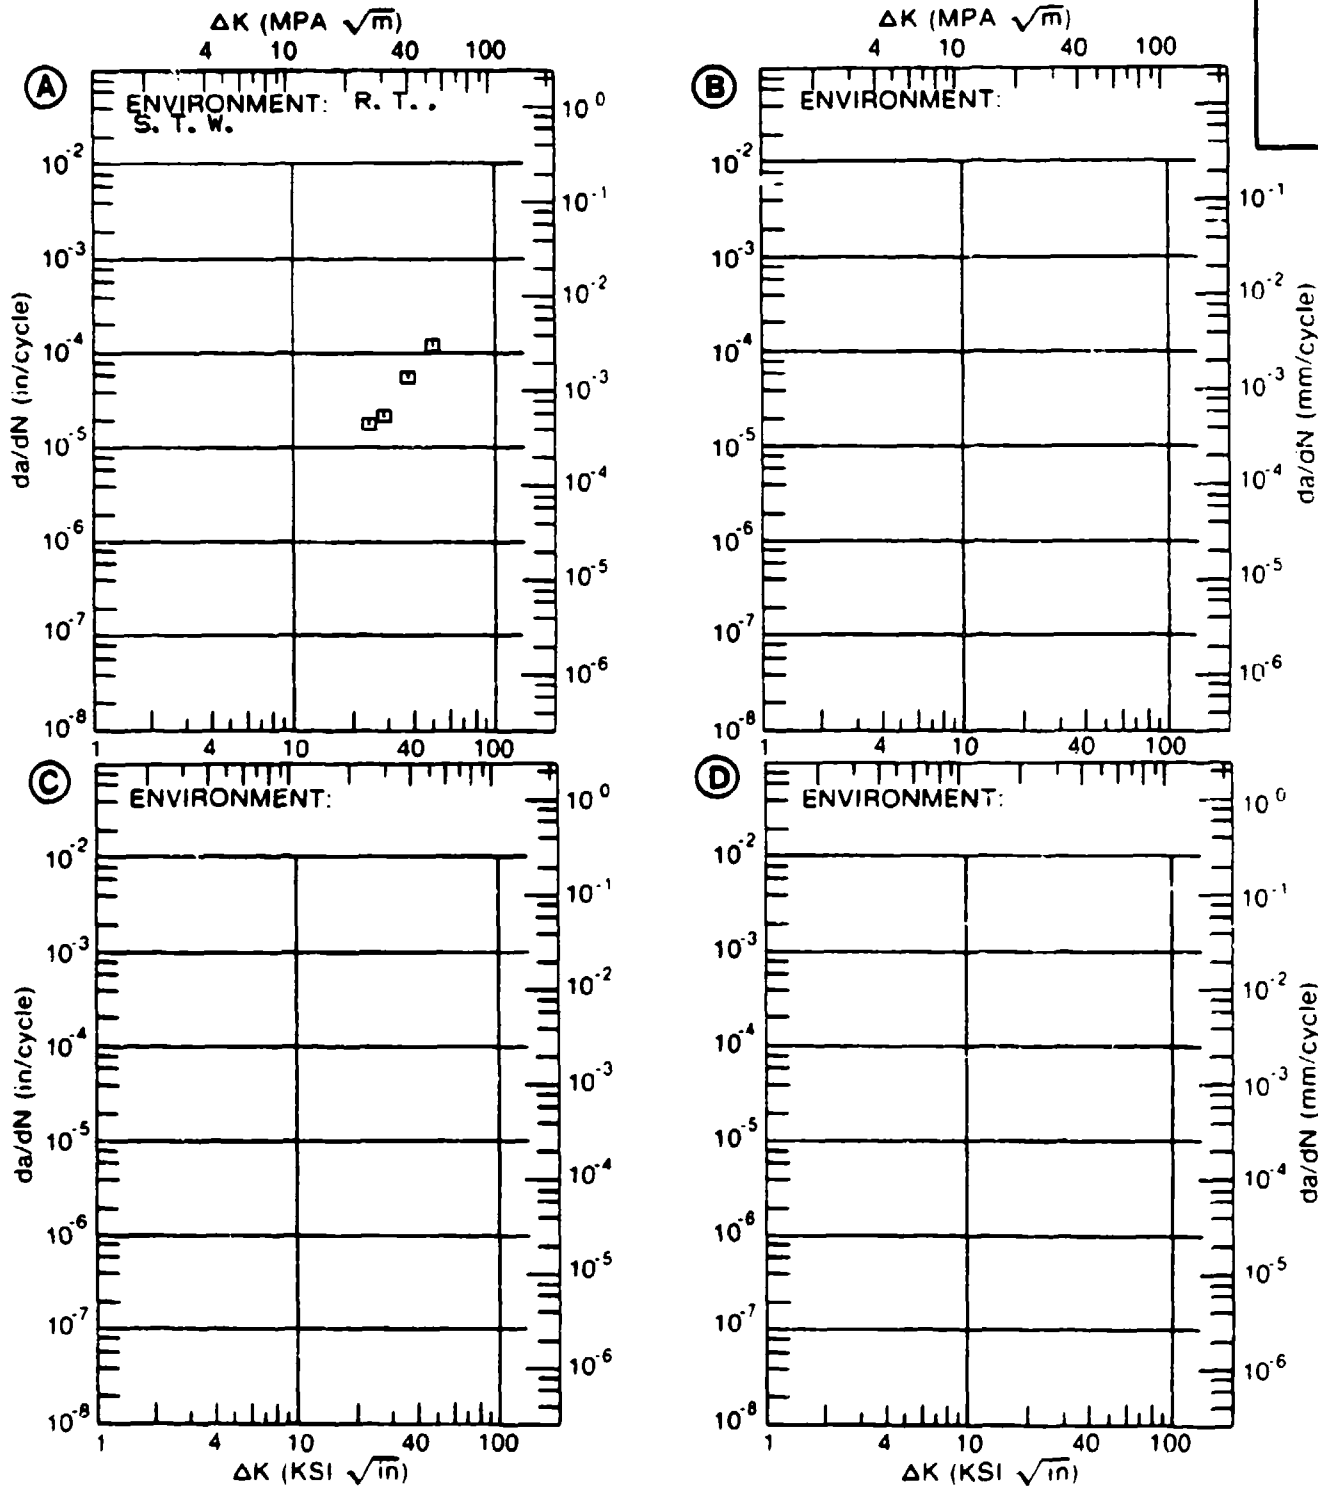


Figure 4.11.3.20

TABLE 4.11.3.21

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.21 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E= R. T. JP-4 FUEL	E= R. T. SIM SEA WATER	
DELTA K A:	10.25	.0872			
DELTA K B:	12.23		.115		
DELTA K C:	10.06			.219	
DELTA K D:					
	13.00	.284	.165	.779	
	14.00	.820	.566	1.94	
	20.00	2.55	2.08	4.82	
	25.00	7.52	6.89	11.6	
	30.00	17.1	16.1	23.8	
	35.00	31.9	28.9	43.1	
	40.00	51.8	44.6	70.5	
	50.00	102.	88.2	149.	
	60.00	183.	168.	254.	
	70.00	356.	339.	438.	
	80.00	794.	736.	933.	
	90.00	2039.	1726.	2619.	
	100.00		4343.		
DELTA K A:	99.83	5876.			
DELTA K B:	101.83		5178.		
DELTA K C:	99.93			9645.	
DELTA K D:					
ROOT MEAN SQUARE		26.01	24.42	25.45	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 1.30" TH FORGING
 SPECIMEN TYPE: WOL
 ORIENTATION: L-T
 STRESS RATIO: +0.02
 FREQUENCY: 0.10- 20.00 HZ

YIELD STRENGTH: 111.0- 111.5 KSI
 ULT. STRENGTH: 122.5- 127.5 KSI
 SPECIMEN THK: 1.250"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: MA005

TITAN.
 ALLOY

TI-6AL-
 4V

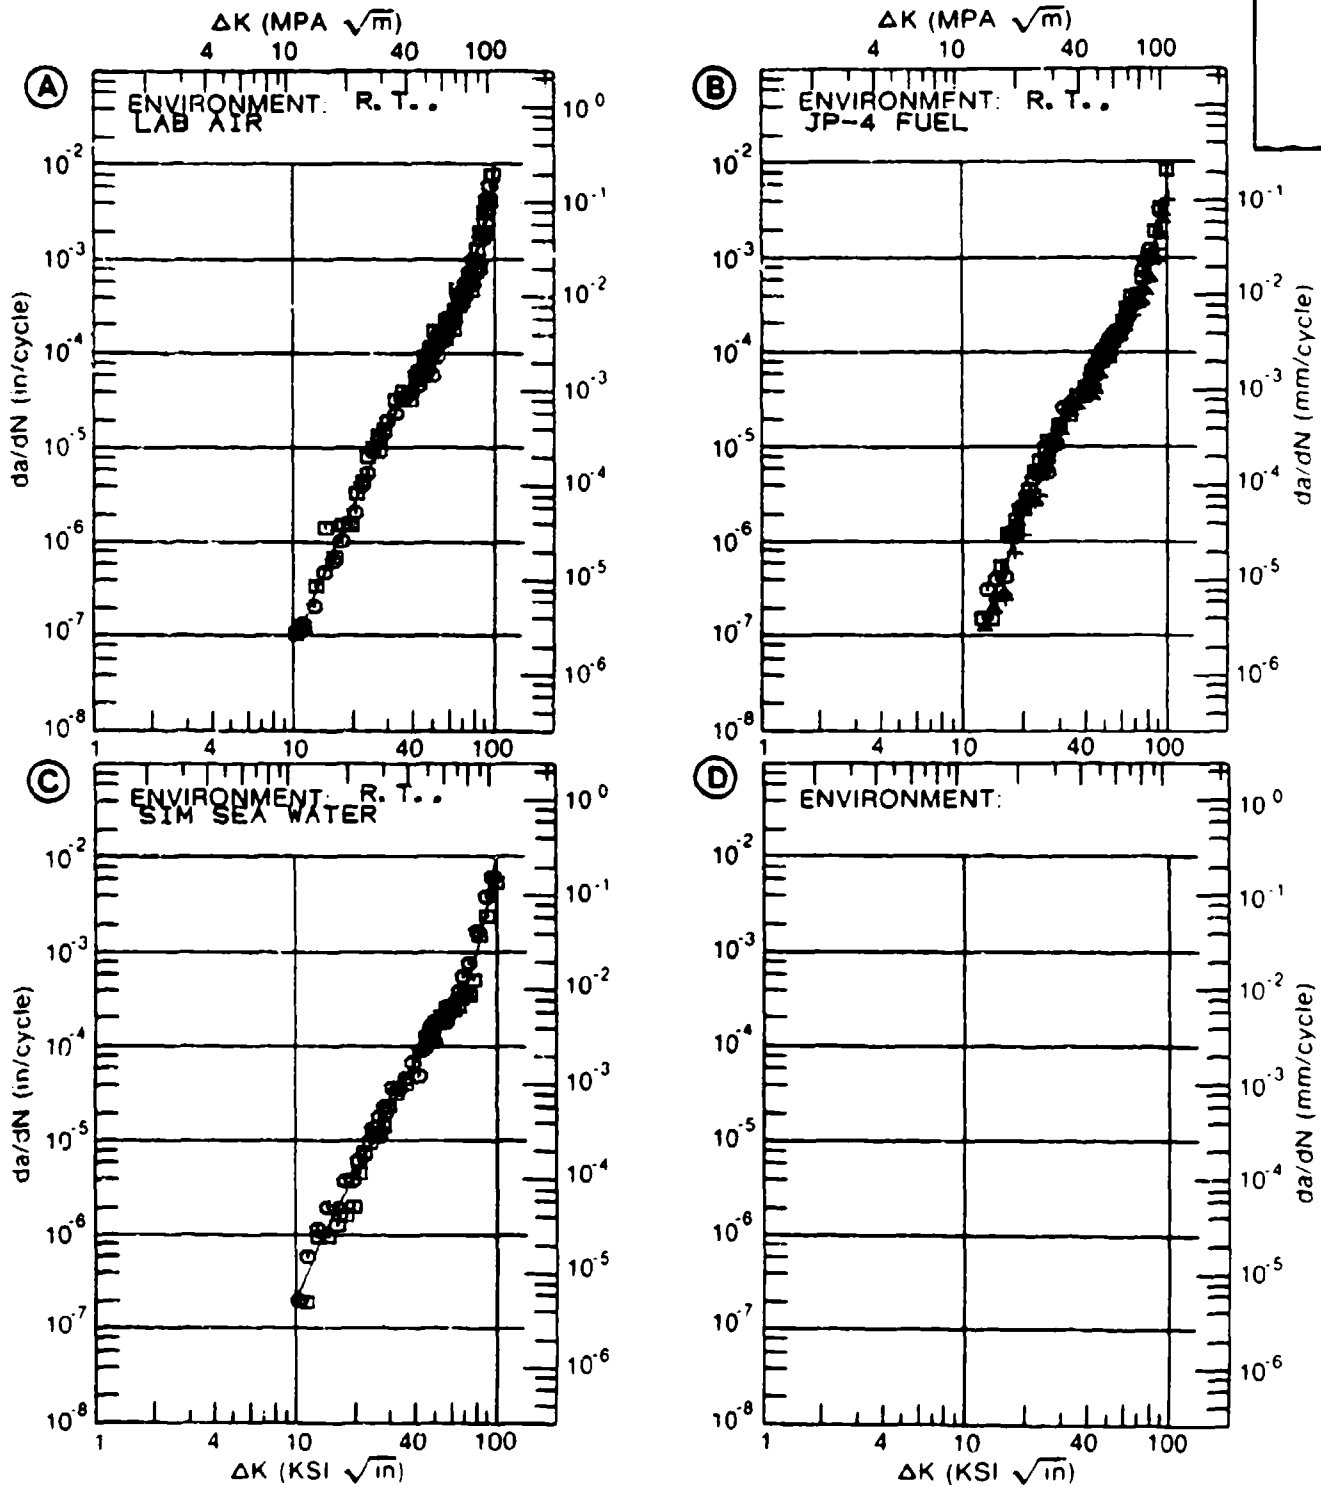


Figure 4.11.3.21

TABLE 4.11.3.22

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.22 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E= R. T. JP-4 FUEL	E= R. T. SIM SEA WATER	
DELTA K	A: 10.97	.0750			
MIN	B: 11.53		.0872		
	C: 10.11			.177	
	D:				
	13.00	.226	.204	.651	
	16.00	.743	.741	1.66	
	20.00	2.27	2.40	4.09	
	25.00	6.15	6.63	9.39	
	30.00	13.1	14.0	18.0	
	35.00	24.3	25.6	31.2	
	40.00	41.5	42.9	50.5	
	50.00	103.	103.	118.	
	60.00	227.	224.	250.	
	70.00	467.	457.	499.	
	80.00	918.	903.	959.	
	90.00	1746.	1743.	1789.	
	100.00	3242.		3259.	
DELTA K	A: 104.34	4214.			
MAX	B: 99.96		3302.		
	C: 102.34			3739.	
	D:				
ROOT MEAN SQUARE		27.58	29.08	34.70	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 1.30" TH FORGING
 SPECIMEN TYPE: WOL
 ORIENTATION: T-L
 STRESS RATIO: +0.02
 FREQUENCY: 0.10- 20.00 HZ

YIELD STRENGTH: 110.0- 110.5 KSI
 ULT. STRENGTH: 124.5- 125.0 KSI
 SPECIMEN THK: 1.250"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: MA005

TITAN.
 ALLOY

TI-6AL-
 4V

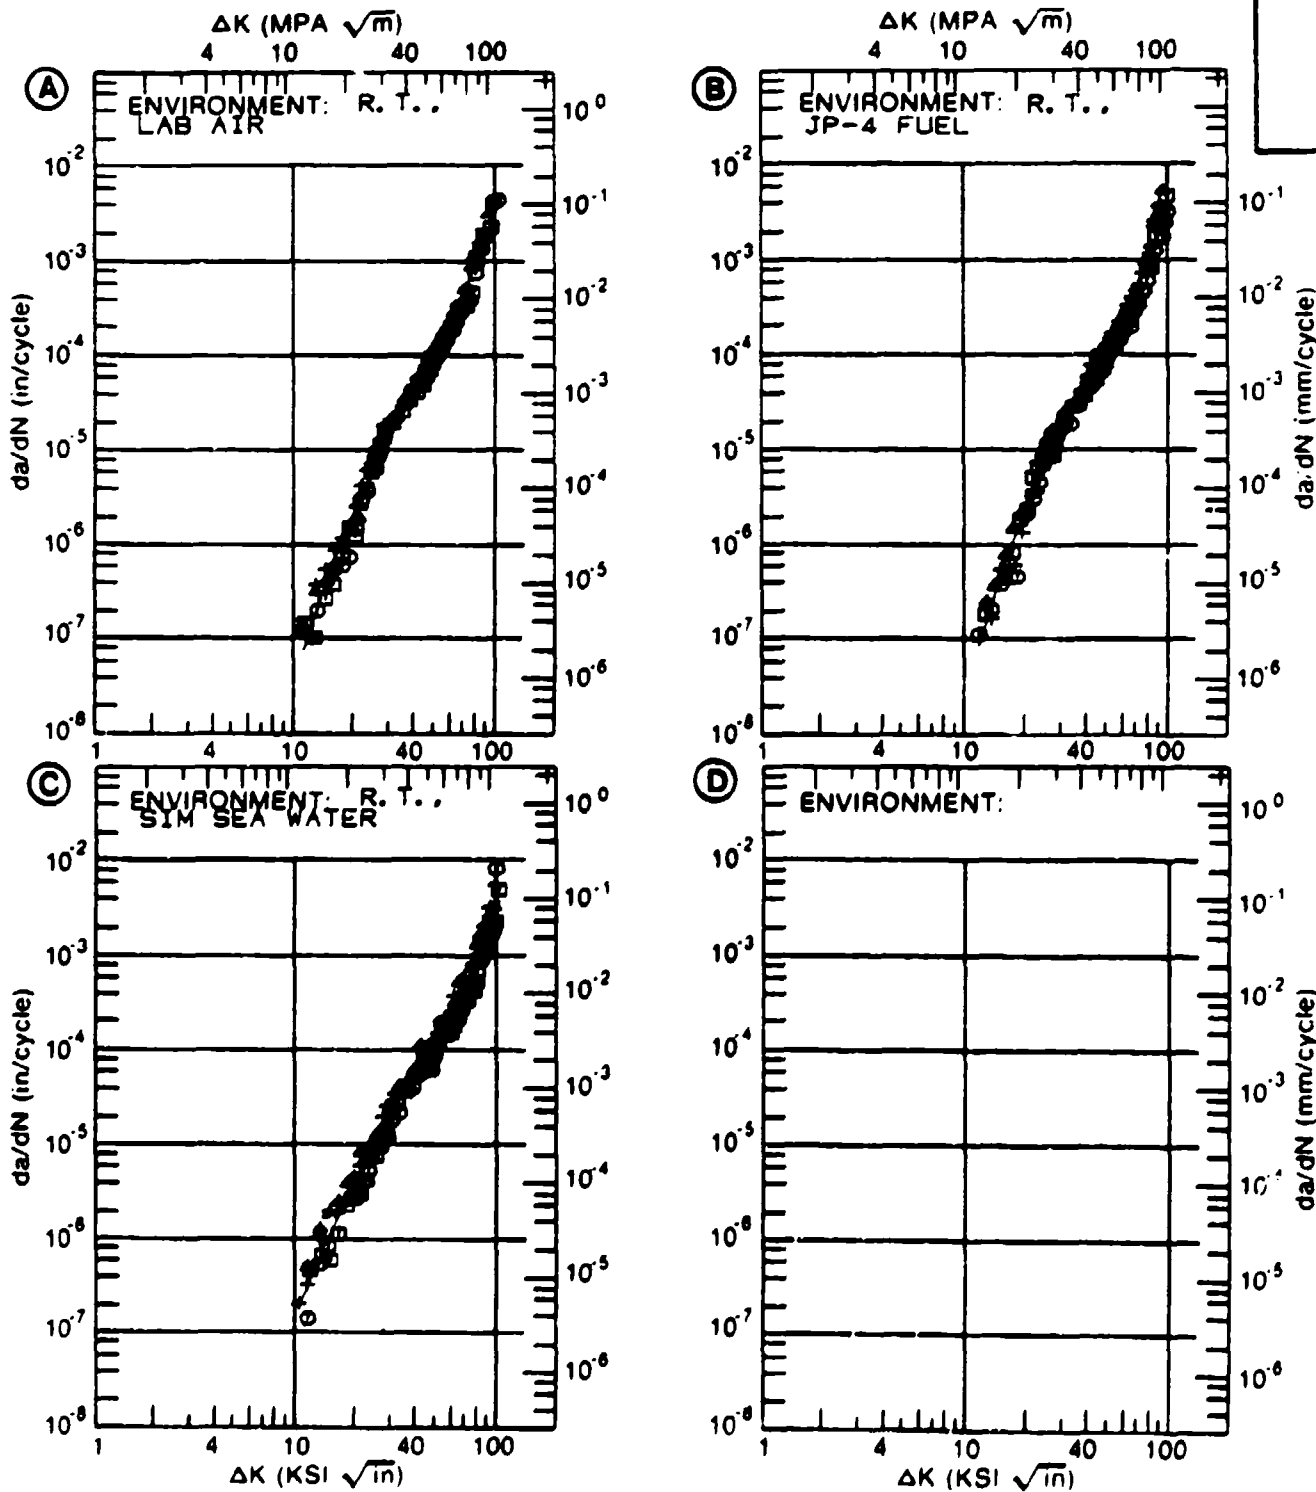


Figure 4.11.3.22

TABLE 4.11.3.23

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.23 INDICATING EFFECT

JF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: BETA PROCESSED-MILL ANNEALED

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E= R. T. DRY AIR			
DELTA K A: 23.05	5.27			
MIN B:				
C:				
D:				
25.00	6.45			
30.00	10.3			
35.00	15.7			
40.00	23.4			
50.00	48.8			
DELTA K A: 59.48	94.0			
MAX B:				
C:				
D:				

ROOT MEAN SQUARE 7.55
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: BETA PROCESSED-MILL ANNEALED
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 01332

TITAN.
 ALLOY

TI-6AL-
 4V

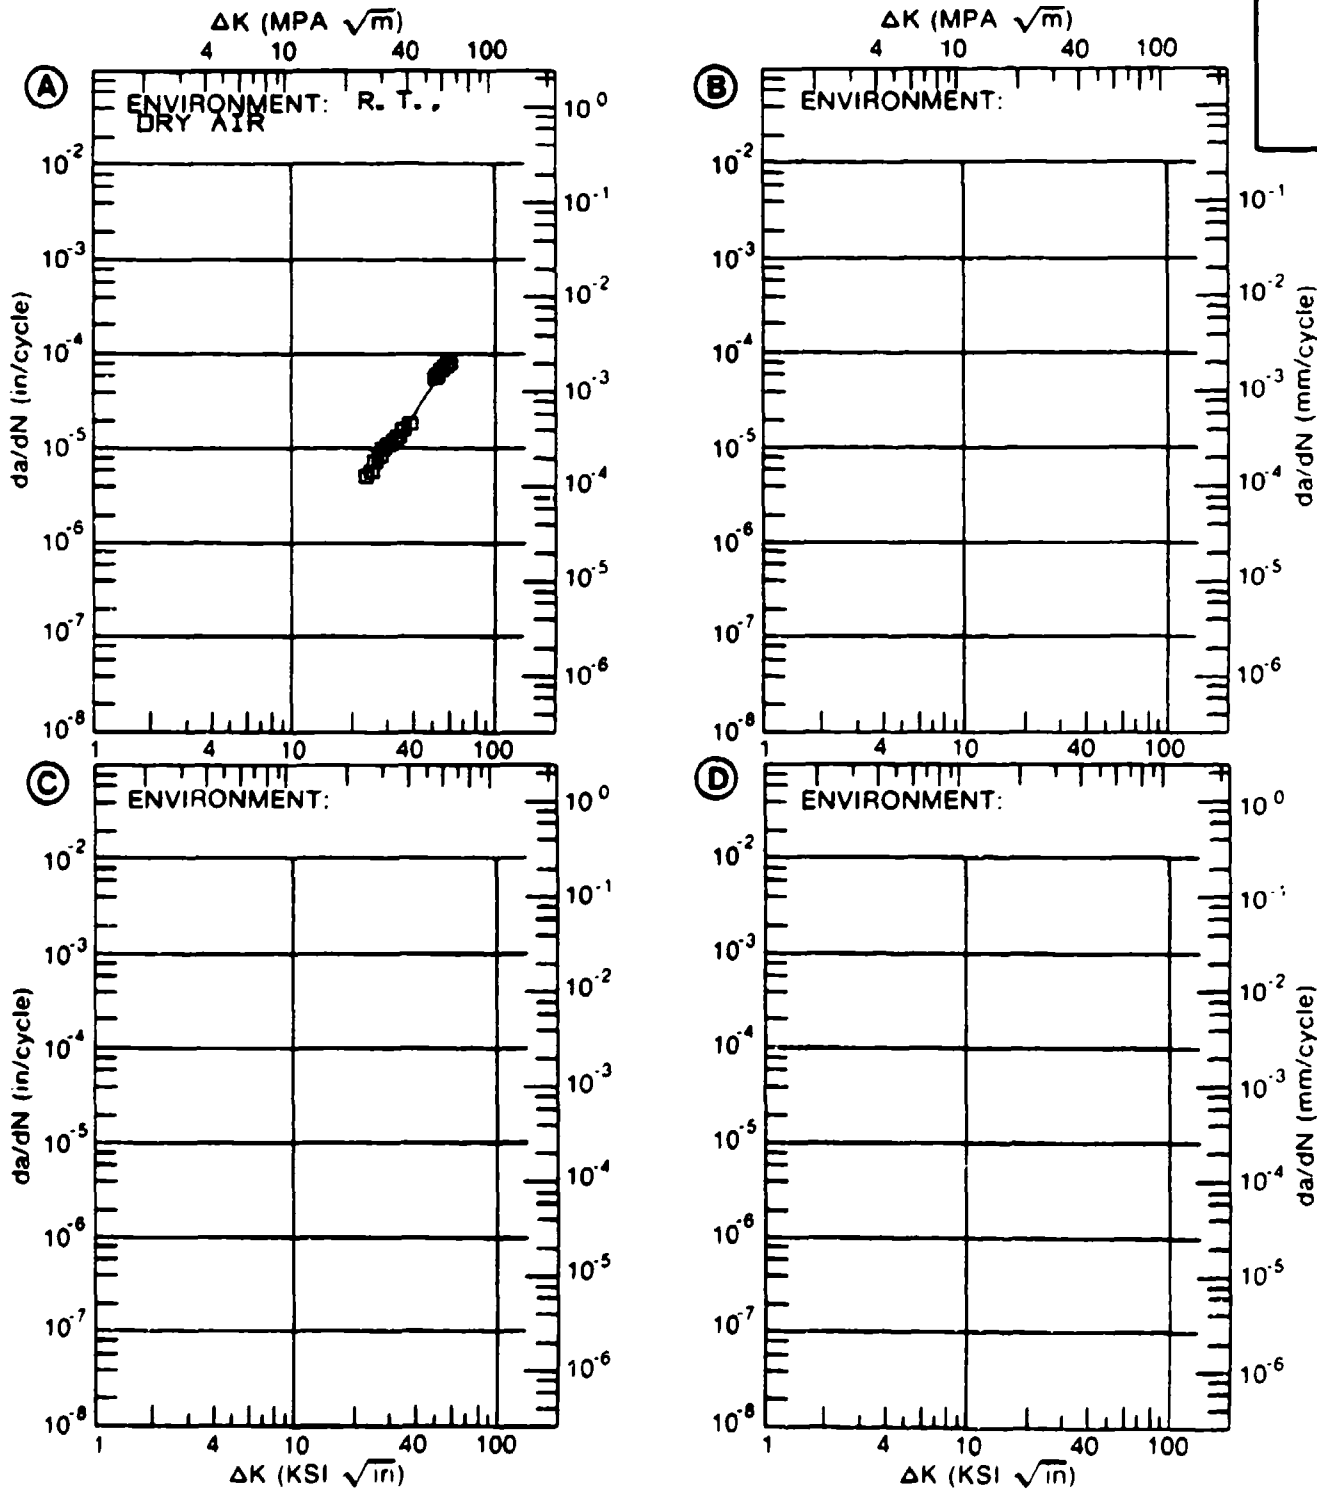


Figure 4.11.3.23

TABLE 4.11.3.24

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.24 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BETA PROCESSED-MILL ANNEALED					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR			
DELTA K	A: 23.71	5.76			
MIN	B:				
	C:				
	D:				
	25.00	6.20			
	30.00	9.23			
	35.00	14.6			
	40.00	22.9			
	50.00	48.7			
	60.00	82.7			
DELTA K	A: 60.18	83.4			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		15.14			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BETA PROCESSED-MILL ANNEALED
 FORM: 0.30" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 91332

TITAN.
 ALLOY

TI-6AL-
 4V

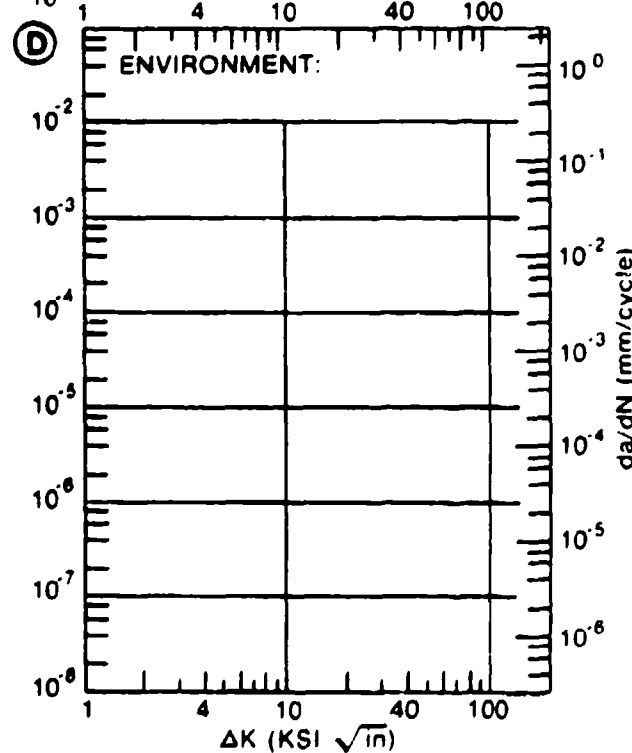
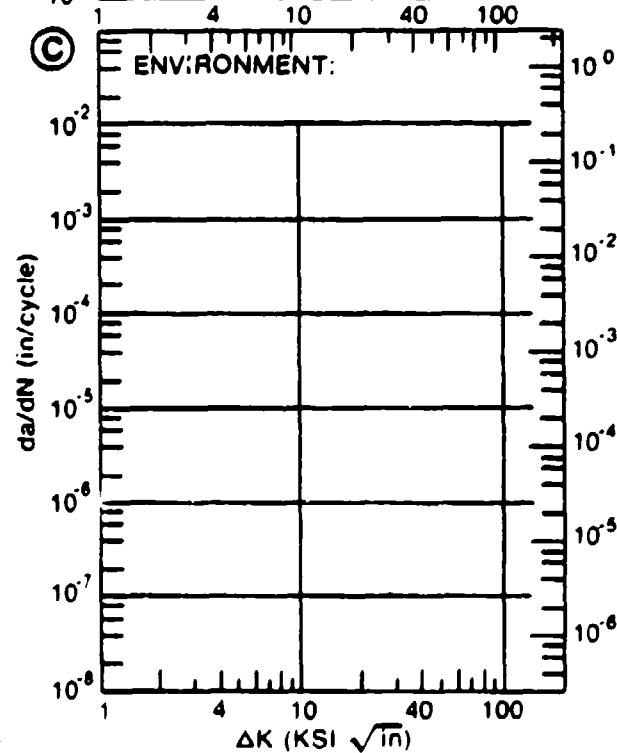
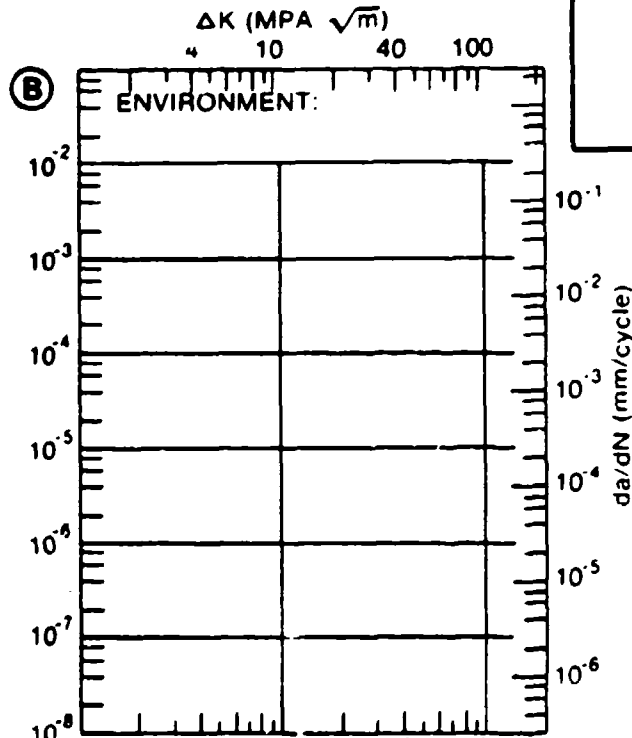
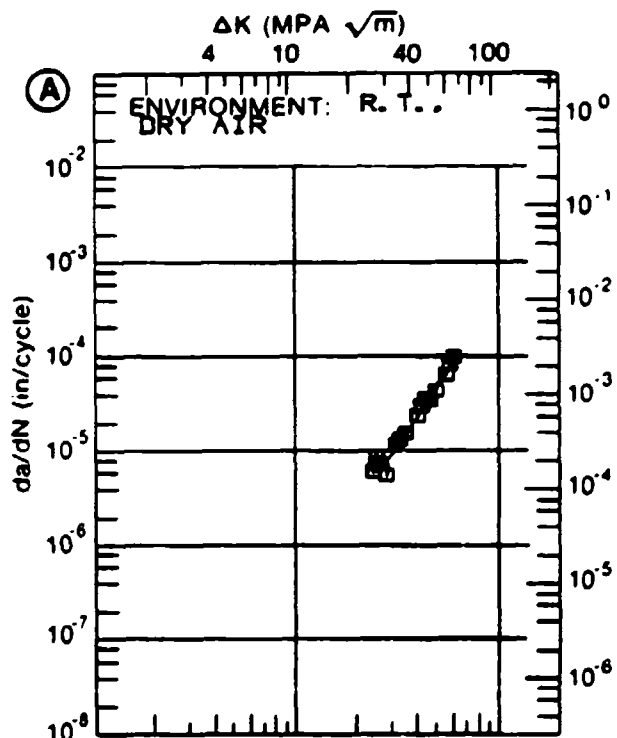


Figure 4.11.3.24

TABLE 4.11.3.25

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.25 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: BETA PROCESSED-MILL ANNEALED
ENVIRONMENT: R. T. , DRY AIR

DELTA K
(KSI*IN**1/2)

DA/DN (10**⁻⁶ IN. /CYCLE)

A

B

C

D

R=+0.10

DELTA K A: 17.02
MIN B:
C:
D:

2.69

20.00

4.51

25.00

9.81

30.00

16.8

35.00

28.4

DELTA K A: 35.59
MAX B:
C:
D:

31.4

ROOT MEAN SQUARE
PERCENT ERROR

7.19

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: BETA PROCESSED-MILL ANNEALED

FORM: 0.50" TH PLATE

SPECIMEN TYPE: CT

ORIENTATION: L-T

FREQUENCY: 10.00 HZ

ENVIRONMENT: R. T., DRY AIR

YIELD STRENGTH:

ULT. STRENGTH:

SPECIMEN THK:

SPECIMEN WIDTH:

REFERENCES 91332

TITAN.
ALLOY

TI-6AL-
4V

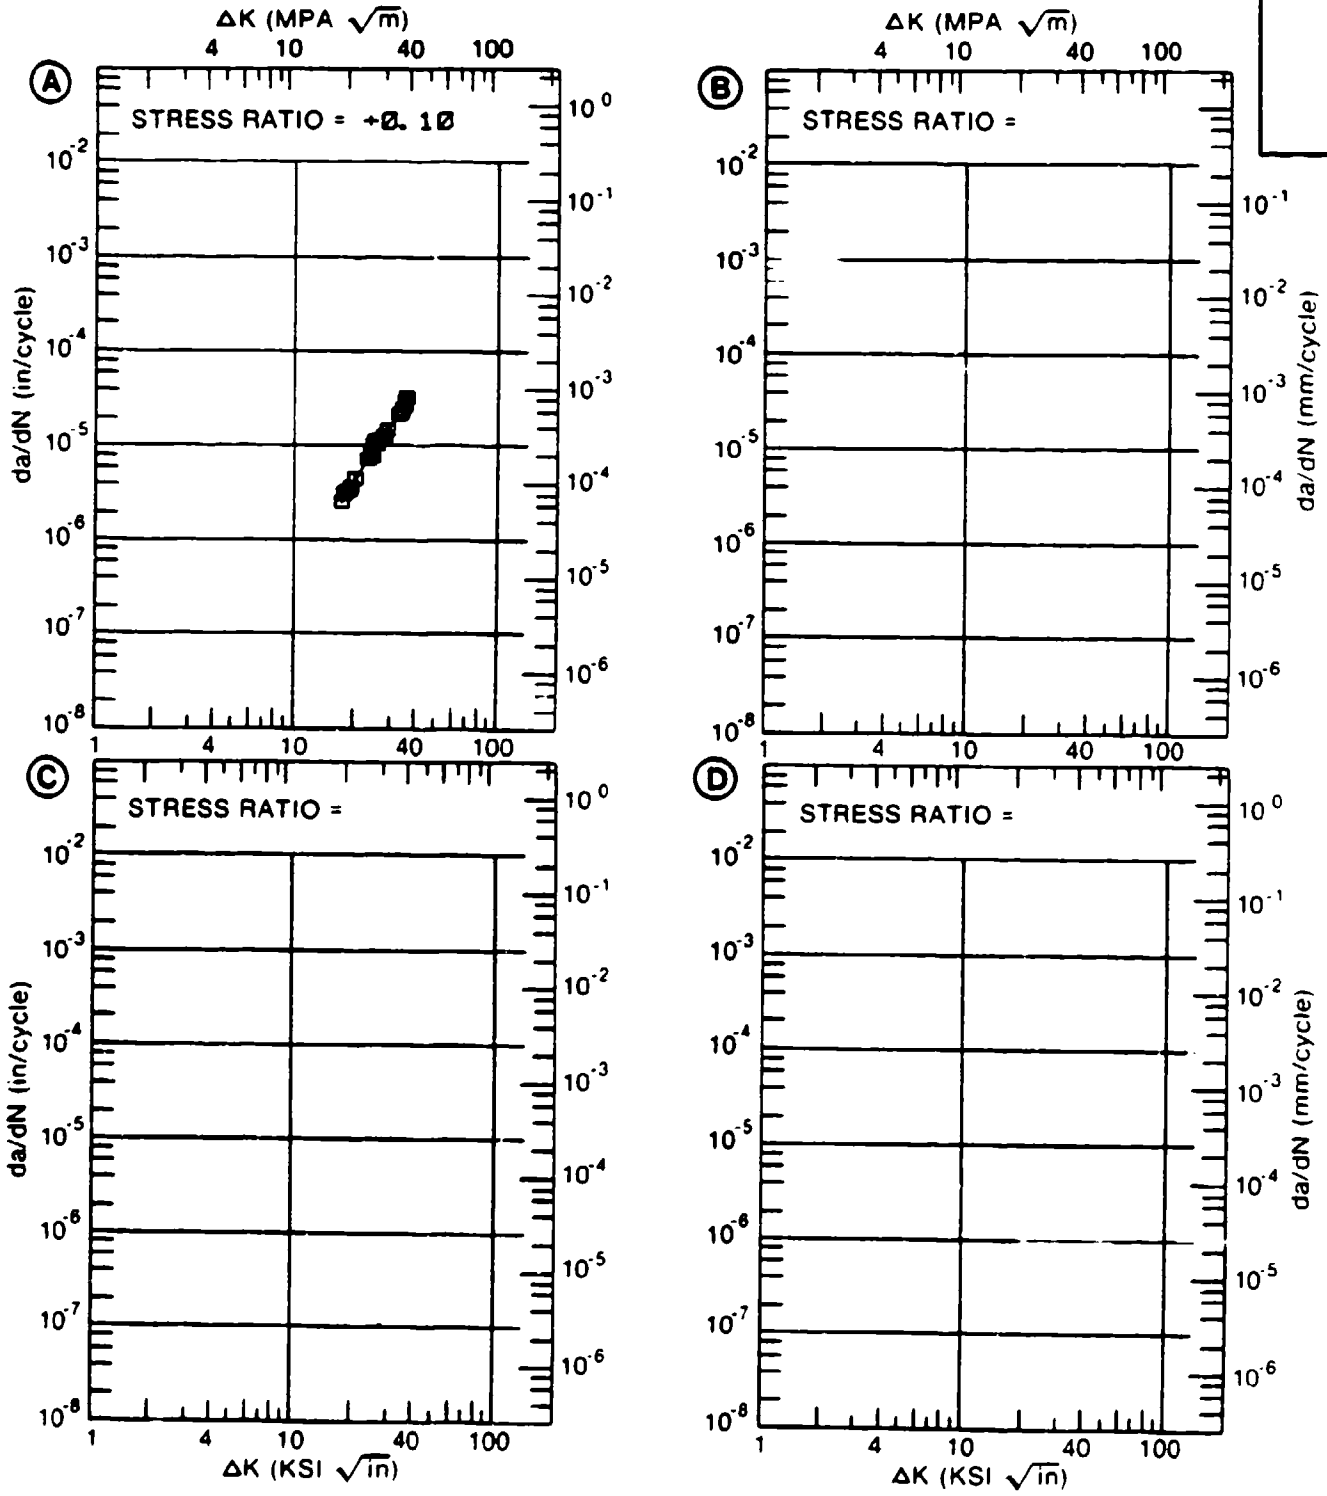


Figure 4.11.3.25

TABLE 4.11.3.26

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.26 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BETA PROCESSED-MILL ANNEALED					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		DRY AIR			
DELTA K	A: 16.77	2.51			
MIN	B:				
	C:				
	D:				
	20.00	4.66			
	25.00	9.56			
	30.00	16.9			
	35.00	27.8			
DELTA K	A: 36.12	30.9			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		6.21			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BETA PROCESSED-MILL ANNEALED

FORM: 0.50" TH PLATE

SPECIMEN TYPE: CT

ORIENTATION: L-T

STRESS RATIO: +0.10

FREQUENCY: 10.00 HZ

YIELD STRENGTH:

ULT. STRENGTH:

SPECIMEN THK:

SPECIMEN WIDTH:

REFERENCES: 01332

TITAN.
ALLOY

TI-6AL-
4V

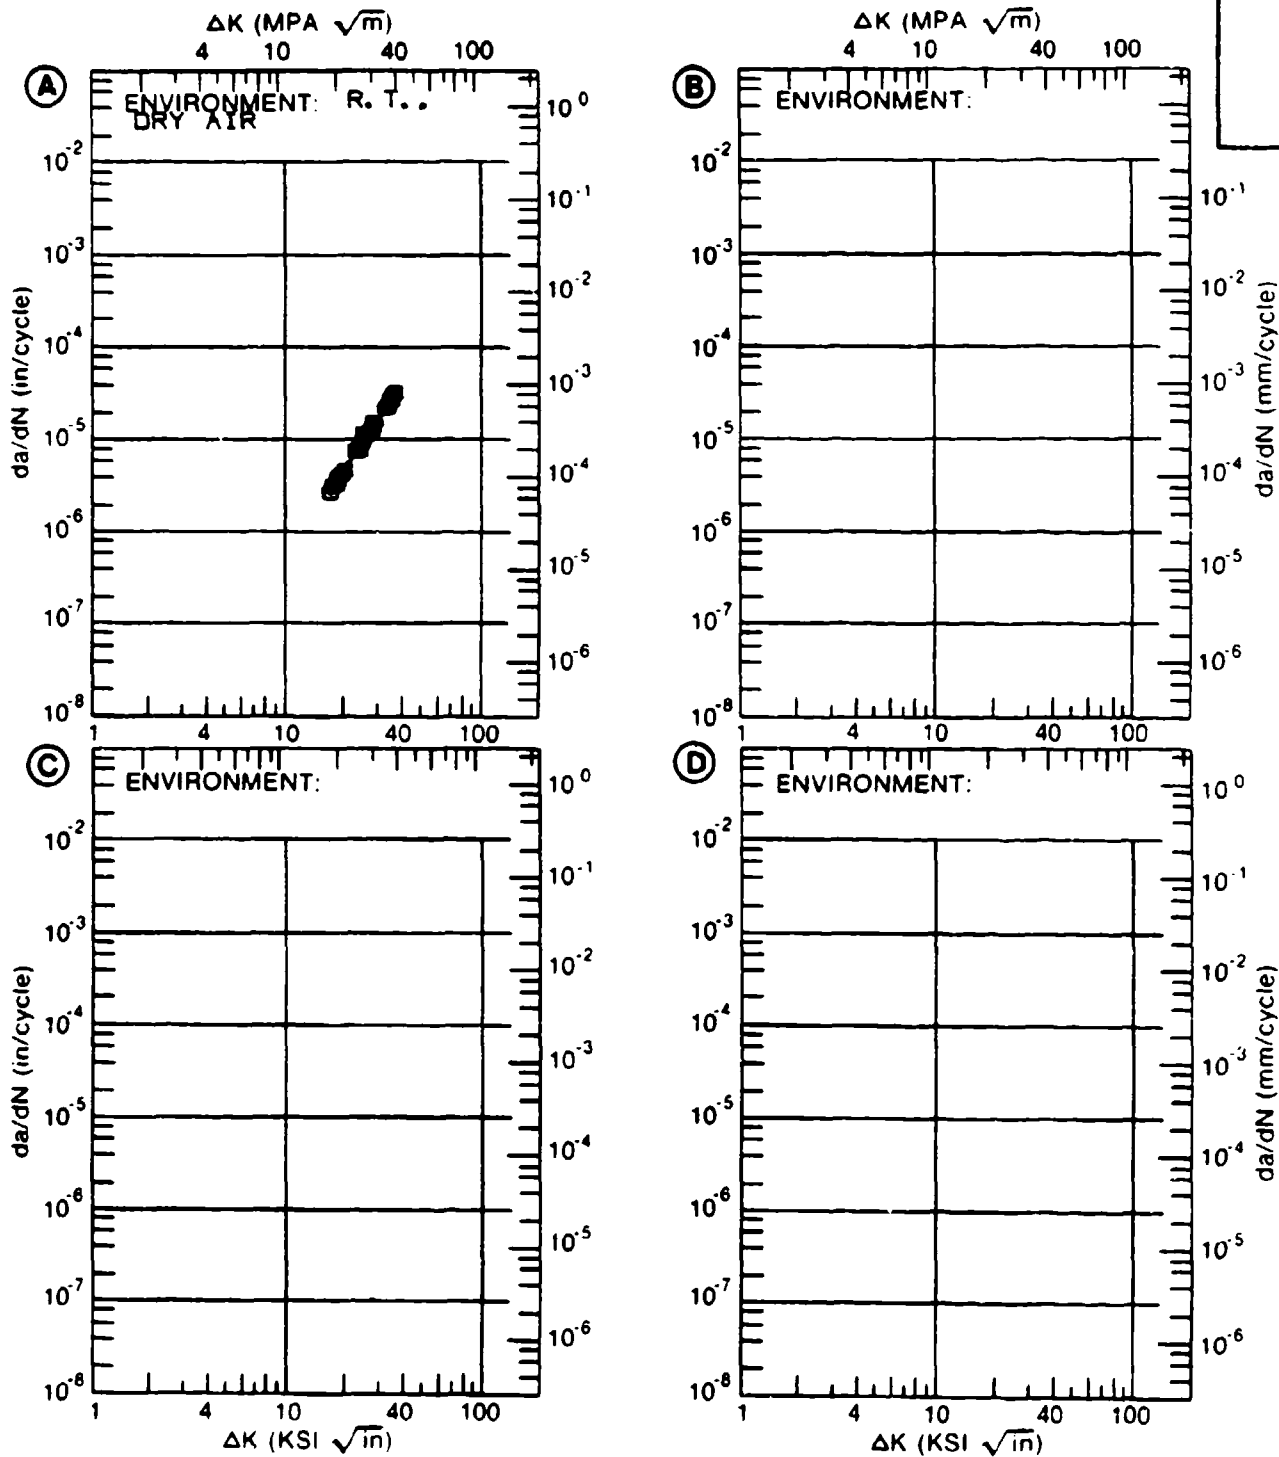


Figure 4.11.3.26

TABLE 4.11.3.27

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.27 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: BETA PROCESSED-MILL ANNEALED					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K A:	14.50	.518			
DELTA K B:	6.57		.0730		
MIN C:					
D:					
	7.00		.133		
	8.00		.387		
	9.00		.827		
	10.00		1.47		
	13.00		4.98		
	16.00	.593	13.6		
	20.00	.917			
	25.00	2.12			
	30.00	6.80			
	35.00	25.7			
DELTA K A:	38.26	43.2			
DELTA K B:	16.76		17.6		
MAX C:					
D:					
ROOT MEAN SQUARE		13.98	18.86		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BETA PROCESSED-MILL ANNEALED

FORM: 3.00" TH PLATE

SPECIMEN TYPE: WOL

ORIENTATION: L-T

FREQUENCY: 1.00 HZ

ENVIRONMENT: R. T. LAB AIR

YIELD STRENGTH: 130.4 KSI

ULT. STRENGTH: 138.1 KSI

SPECIMEN THK: 1.000"

SPECIMEN WIDTH: 2.550"

REFERENCES: JD008

TITAN.
ALLOY

TI-6AL-
4V

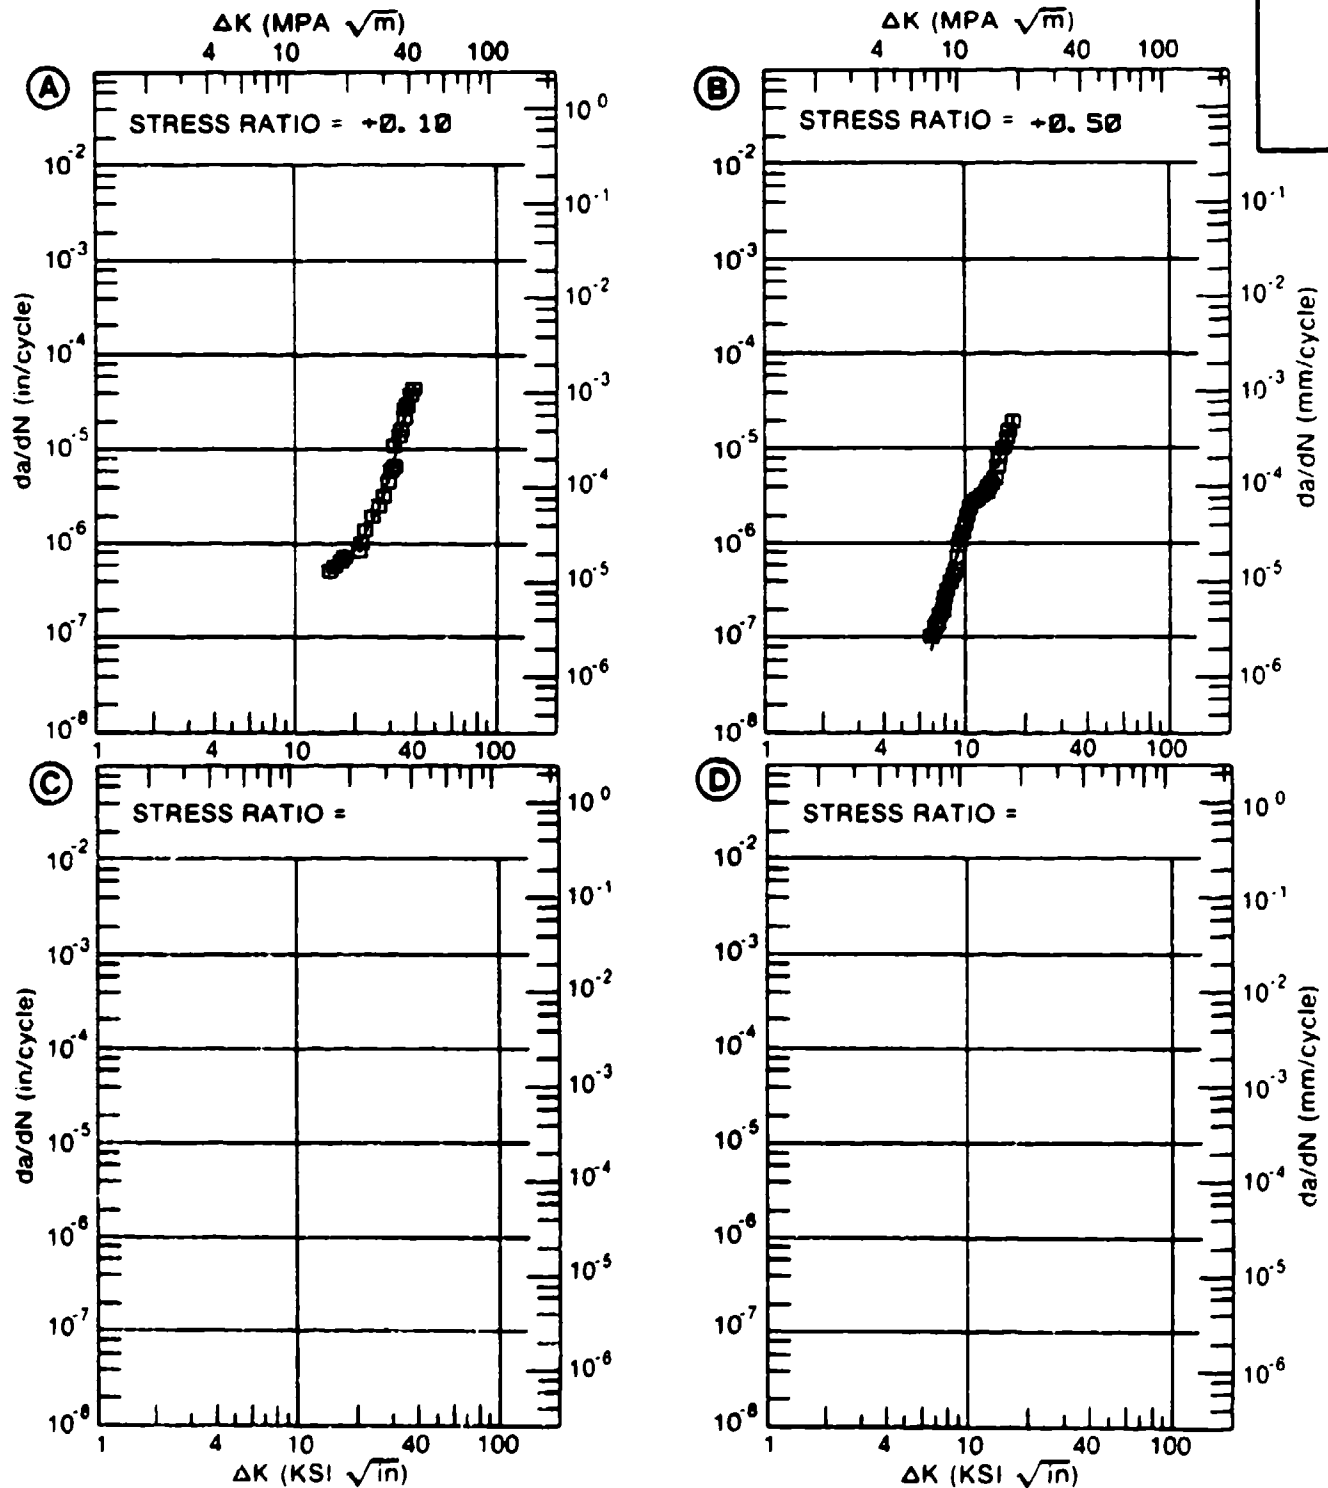


Figure 4.11.3.27

TABLE 4.11.3.28

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.28 INDICATING EFFECT
OF FREQUENCY

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: DB
ENVIRONMENT: R. T. , L. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	F(HZ)= 6.00			
DELTA K MIN	A: 13.23	14.0		
	B: 16.00	21.7		
	C: 20.00	33.1		
	D: 25.00	61.3		
		30.00	144.	
		35.00	415.	
DELTA K MAX	A: 37.82	1316.		
	B:			
	C:			
	D:			

ROOT MEAN SQUARE 12.23
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: DB
 FORM: 0.63" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.30
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 153.0 KSI
 ULT. STRENGTH: 165.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 88579

TITAN.
 ALLOY
 TI-6AL-
 4V

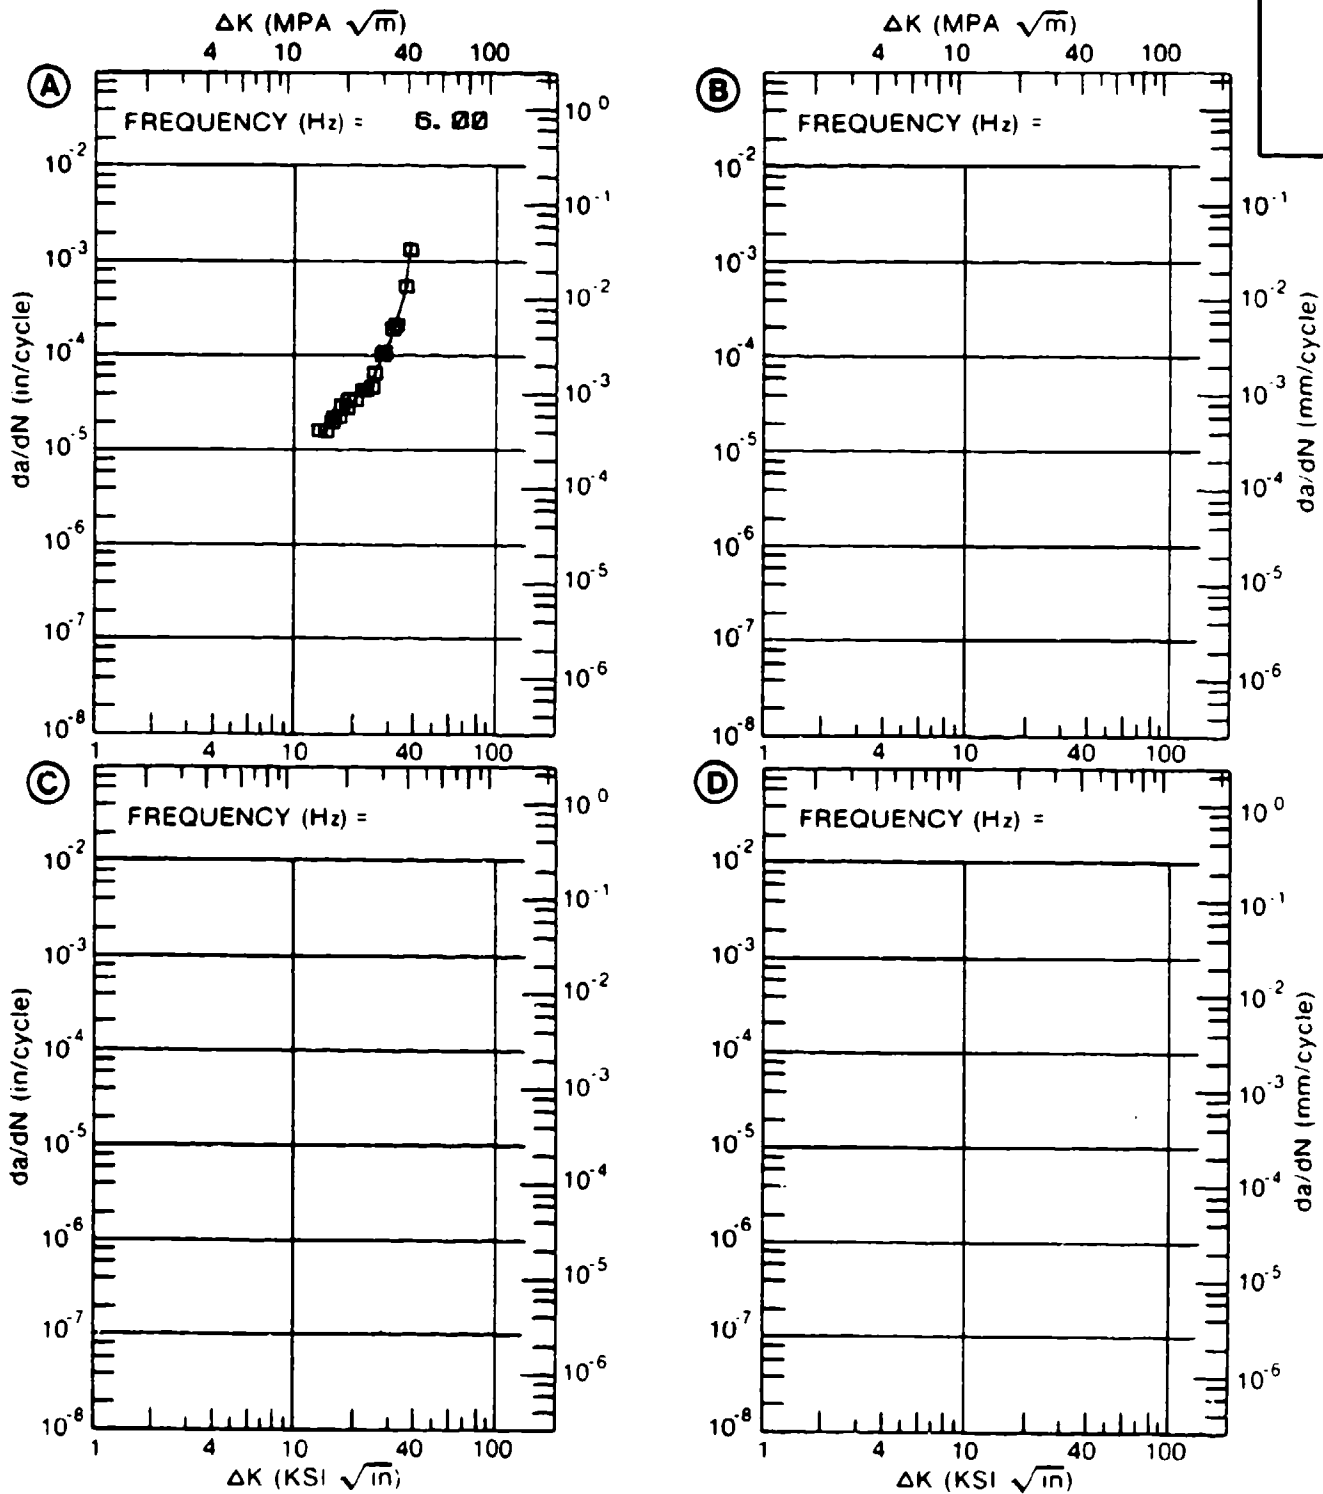


Figure 4.11.3.28

TABLE 4.11.3.29

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.29 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: DB

TI-6AL-4V

DELTA K (KSI*(N**1/2))	DA/DN (10**--6 IN./CYCLE)			
	A	B	C	D
	E= R. T.			
	L. H. A.			
A: 7.88	.139			
DELTA K B:				
MIN C:				
D:				
8.00	.147			
9.00	.242			
10.00	.397			
13.00	1.52			
16.00	4.41			
20.00	12.1			
25.00	25.6			
30.00	35.2			
A: 32.73	36.6			
DELTA K B:				
MAX C:				
D:				
ROOT MEAN SQUARE	17.52			
PERCENT ERROR				

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

1

CONDITION/HT: DB
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 8.00 HZ

YIELD STRENGTH: 115.0 KSI
 ULT. STRENGTH: 126.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 4.040"
 REFERENCES: 98579

TITAN.
 ALLOY
 TI-6AL-
 4V

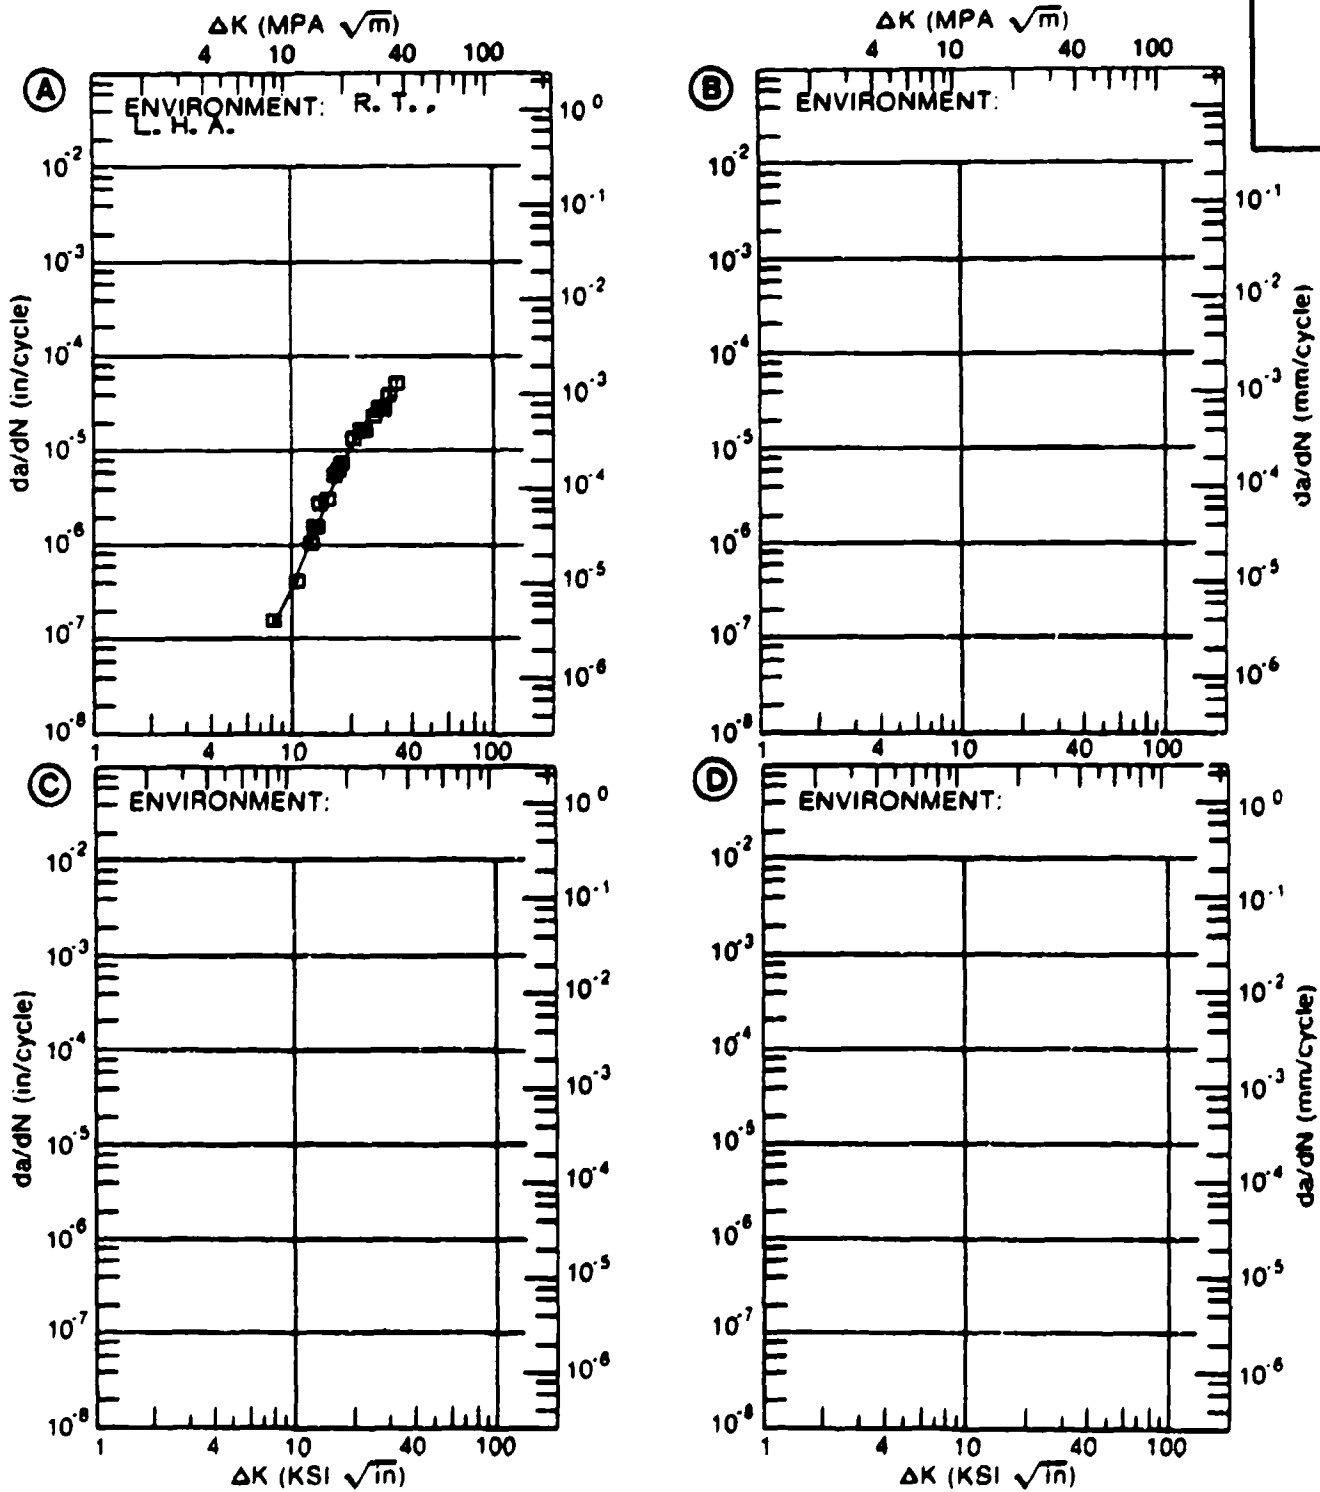


Figure 4.11.3.29

TABLE 4.11.3.30

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.30 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: DB

TI-6AL-4V

DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		S. T. W.			
DELTA K MIN	A: 12.21	.149			
	B:				
	C:				
	D:				
	13.00	.469			
	16.00	1.98			
	20.00	8.20			
	25.00	22.2			
	30.00	41.4			
	35.00	65.8			
	40.00	98.3			
	50.00	214.			
DELTA K MAX	A: 54.03	296.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		19.51			
PERCENT ERROR					

LIFE PREDICTION RATIO	0.0-0.5	
SUMMARY (NP/NA)	0.5-0.8	
	0.8-1.25	1
	1.25-2.0	
	>2.0	

CONDITION/HT: DB
 FORM: 8.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 118.0 KSI
 ULT. STRENGTH: 128.0 KSI
 SPECIMEN THK: 0.992"
 SPECIMEN WIDTH: 8.020"
 REFERENCES: 85837

TITAN.
 ALLOY

TI-6AL-4V

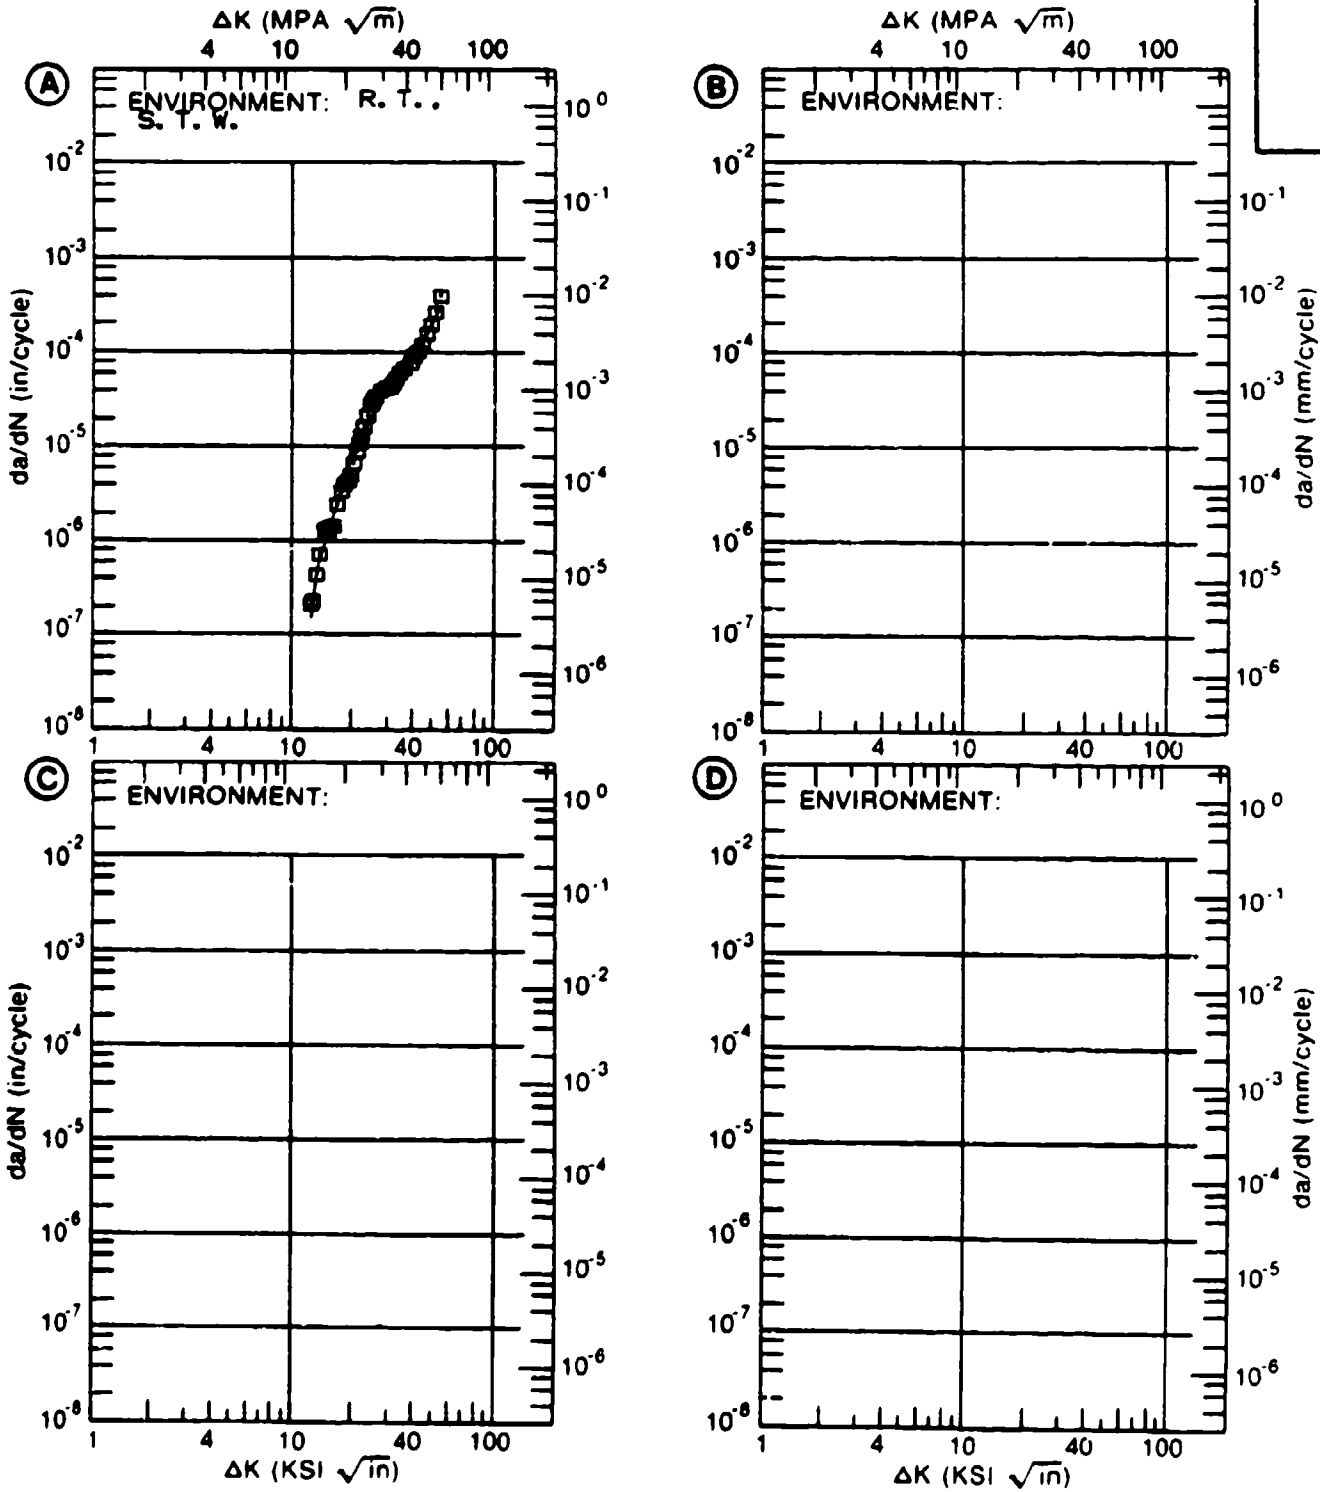


Figure 4.11.3.30

TABLE 4.11.3.31

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.31 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: DB					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		S. T. W.			
DELTA K	A: 9.39	.371			
MIN	B:				
	C:				
	D:				
	10.00	.782			
	13.00	4.03			
	16.00	11.4			
	20.00	21.3			
	25.00	31.5			
	30.00	46.2			
	35.00	77.1			
	40.00	151.			
DELTA K	A: 47.88	497.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		9.26			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: DB
 FORM: 8.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: S-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 114.0 KSI
 ULT. STRENGTH: 129.0 KSI
 SPECIMEN THK: 0.993"
 SPECIMEN WIDTH: 4.940"
 REFERENCES: 85837

TITAN.
 ALLOY

TI-6AL-
 4V

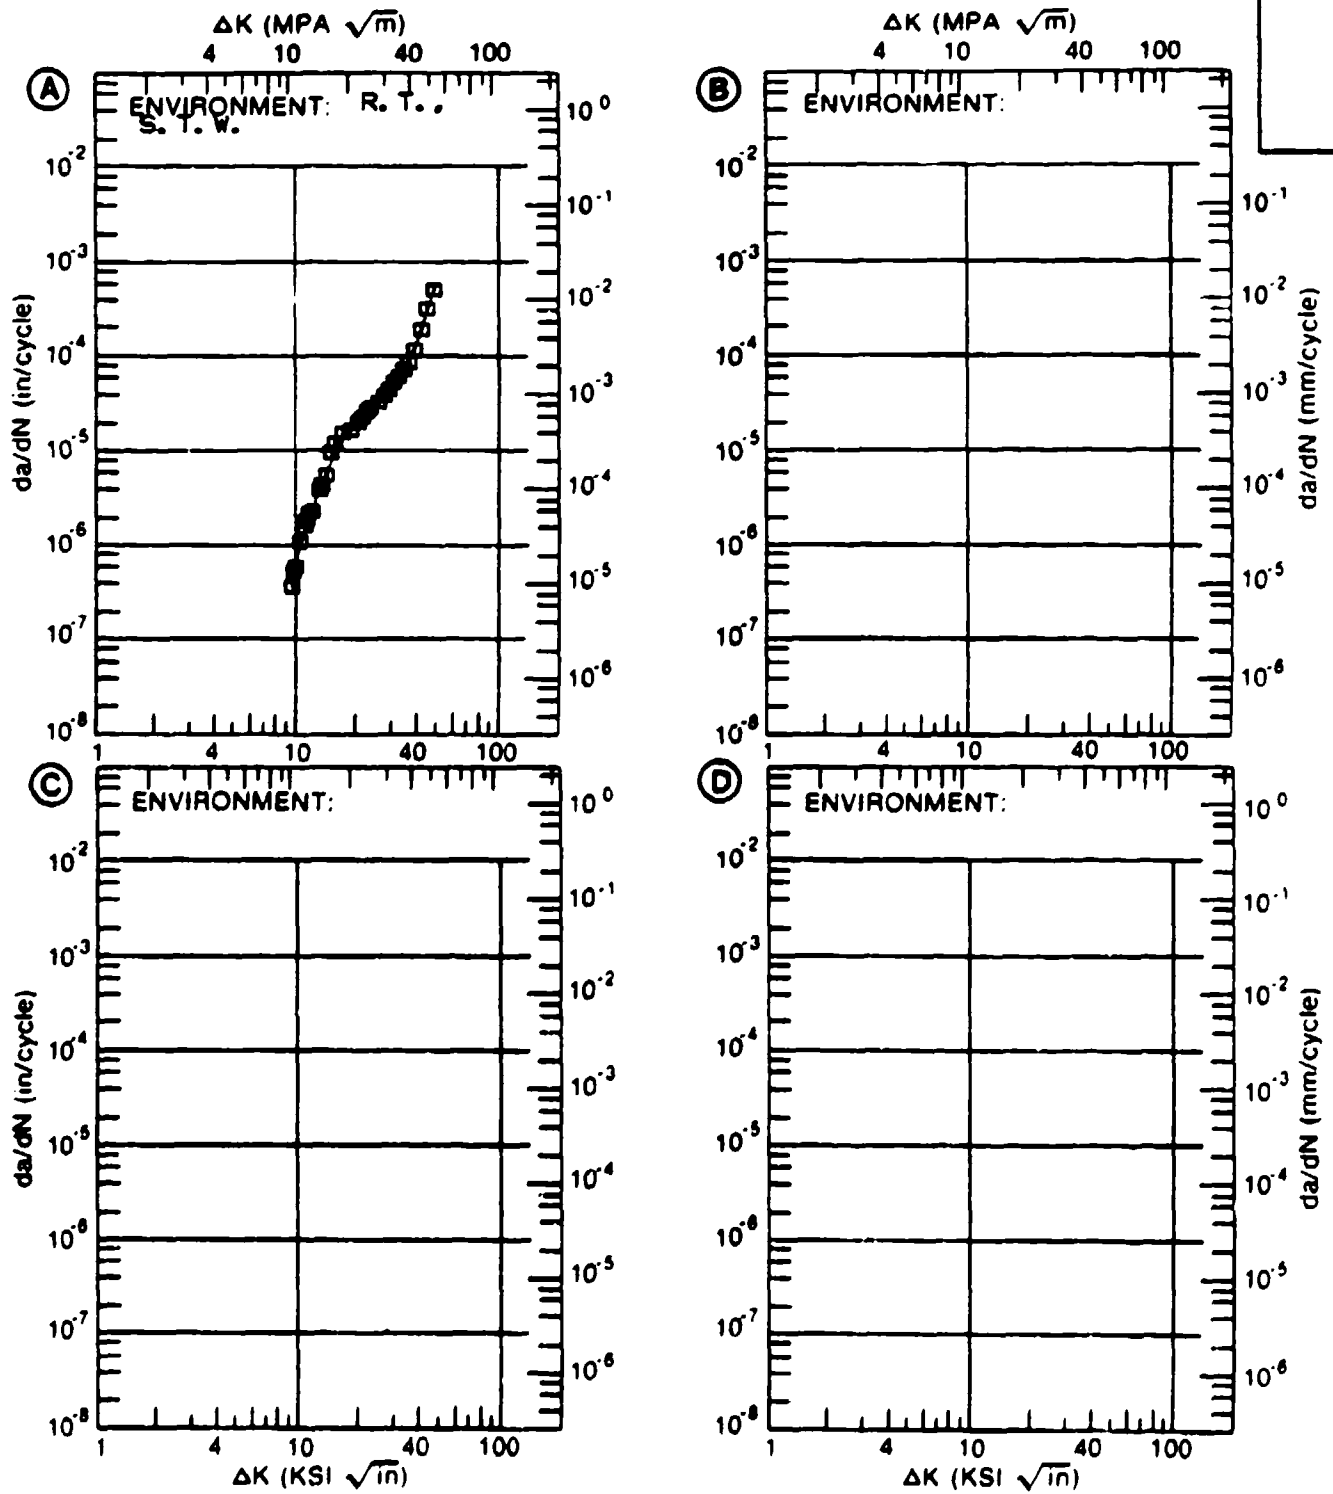


Figure 4.11.3.31

TABLE 4.11.3.32

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.32 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: DB + TR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		S. T. W.			
DELTA K	A: 10.12	.176			
MIN	B:				
	C:				
	D:				
	13.00	.448			
	16.00	2.01			
	20.00	9.78			
	25.00	29.1			
	30.00	50.6			
	35.00	83.1			
	40.00	155.			
DELTA K	A: 44.78	337.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		15.89			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25 1				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: DB + TR
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: S-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 111.0 KSI
 ULT. STRENGTH: 128.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 88579

TITAN.
 ALLOY
 TI-6AL-
 4V

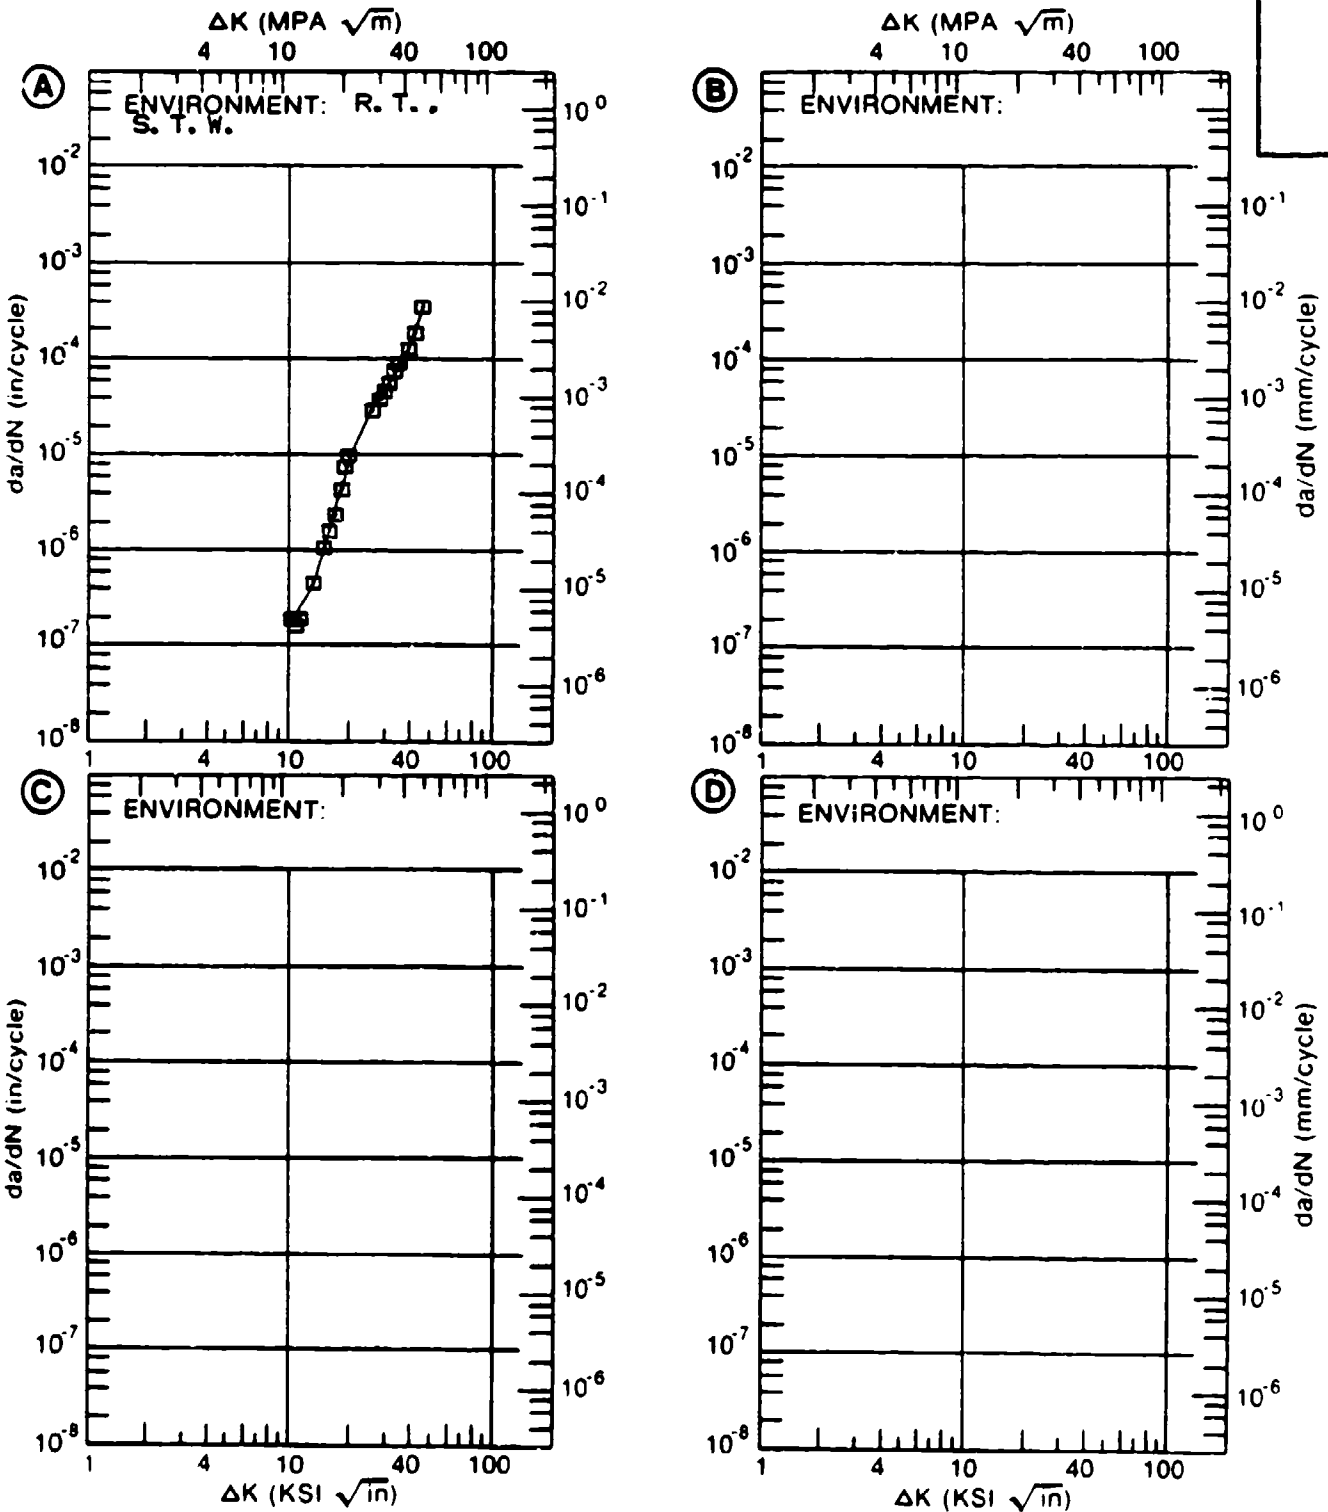


Figure 4.11.3.32

TABLE 4.11.3.33

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.33 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: DB + 2DBTC					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		S. T. W.			
DELTA K	A: 13.92	1.11			
MIN	B:				
	C:				
	D:				
	16.00	2.14			
	20.00	7.93			
	25.00	23.1			
	30.00	45.2			
	35.00	74.0			
	40.00	112.			
	50.00	244.			
	60.00	545.			
DELTA K	A: 62.46	671.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		6.56			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: DB + 2DBTC
 FORM: 8.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 114.0 KSI
 ULT. STRENGTH: 128.0 KSI
 SPECIMEN THK: 0.998"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 85837

TITAN.
ALLOY

TI-6AL-4V

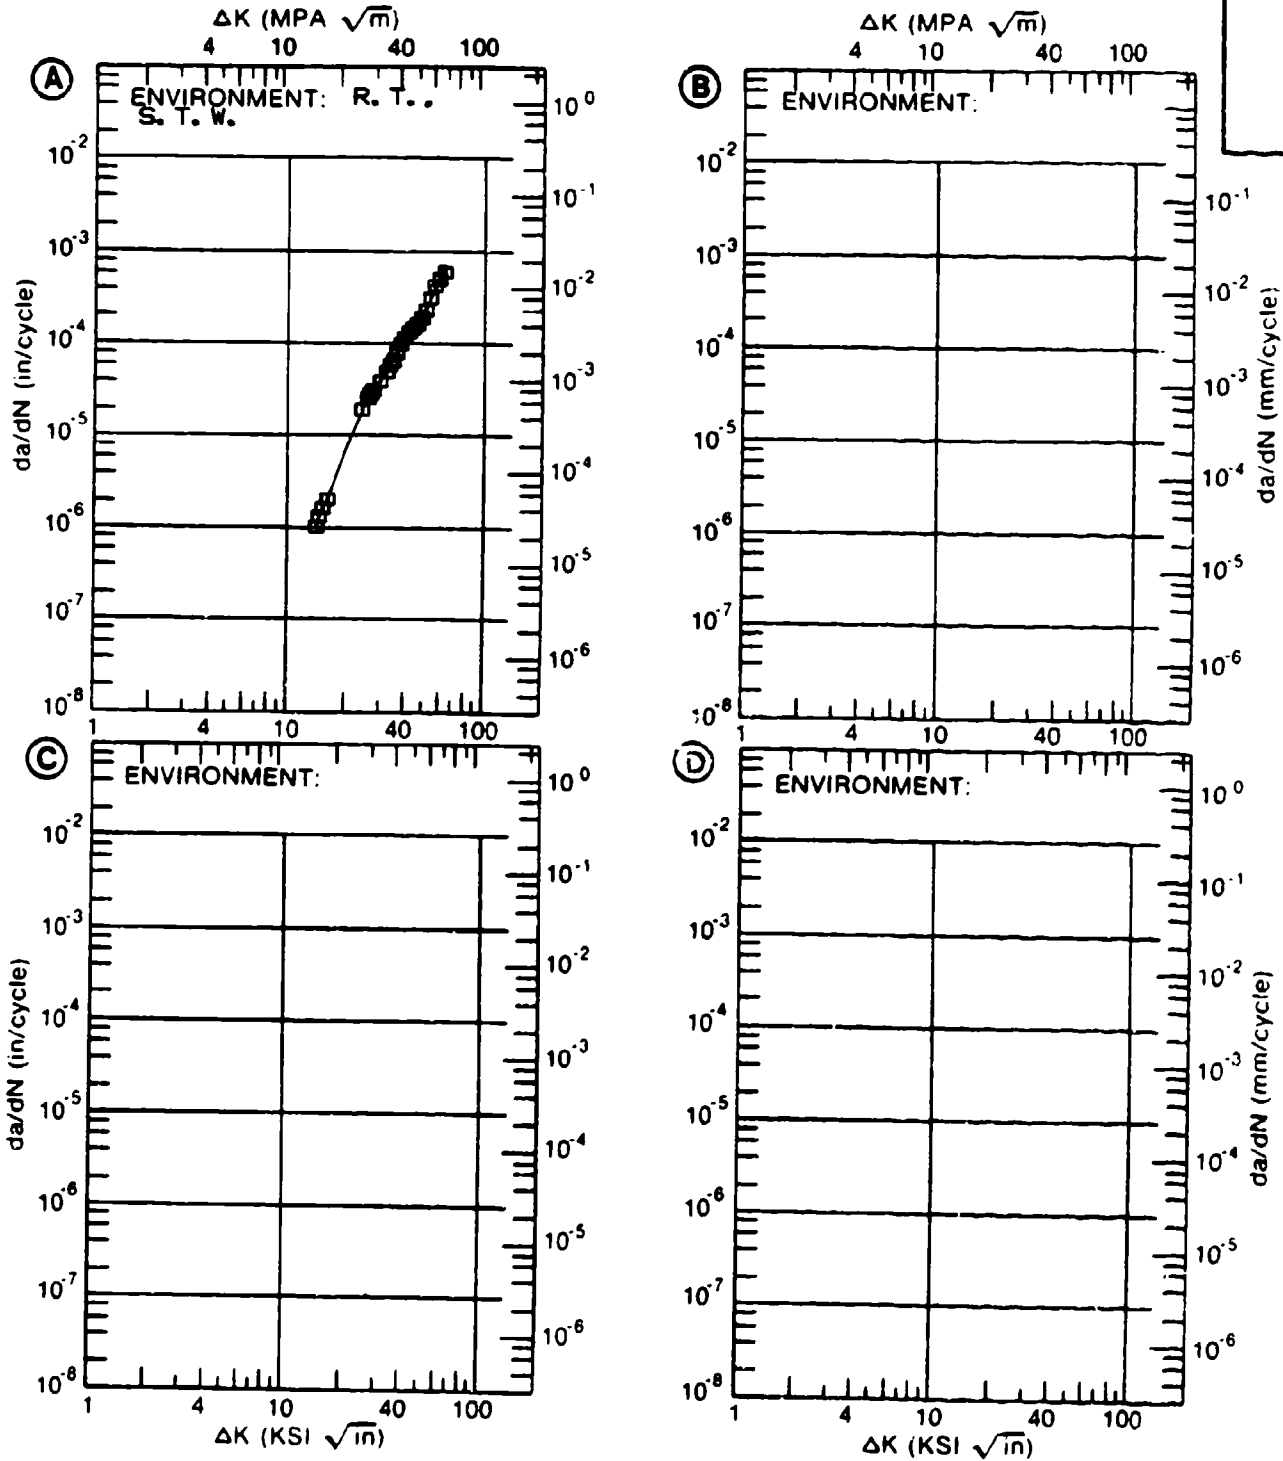


Figure 4.11.3.33

TABLE 4.11.3.34

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.34 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: DB + 2DBTC					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T.			
		L. H. A.			
DELTA K	A: 14.18	2.57			
MIN	B:				
	C:				
	D:				
	16.00	5.81			
	20.00	8.36			
	25.00	30.9			
DELTA K	A: 26.83	31.9			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		16.76			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: DB + 2DBTC
 FORM: 8.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: S-T
 STRESS RATIO: +0.08
 FREQUENCY: 8.00 HZ

YIELD STRENGTH: 114.0 KSI
 ULT. STRENGTH: 128.0 KSI
 SPECIMEN THK: 0.983"
 SPECIMEN WIDTH: 4.950"
 REFERENCES: 85837

TITAN.
 ALLOY

TI-8AL-
 4V

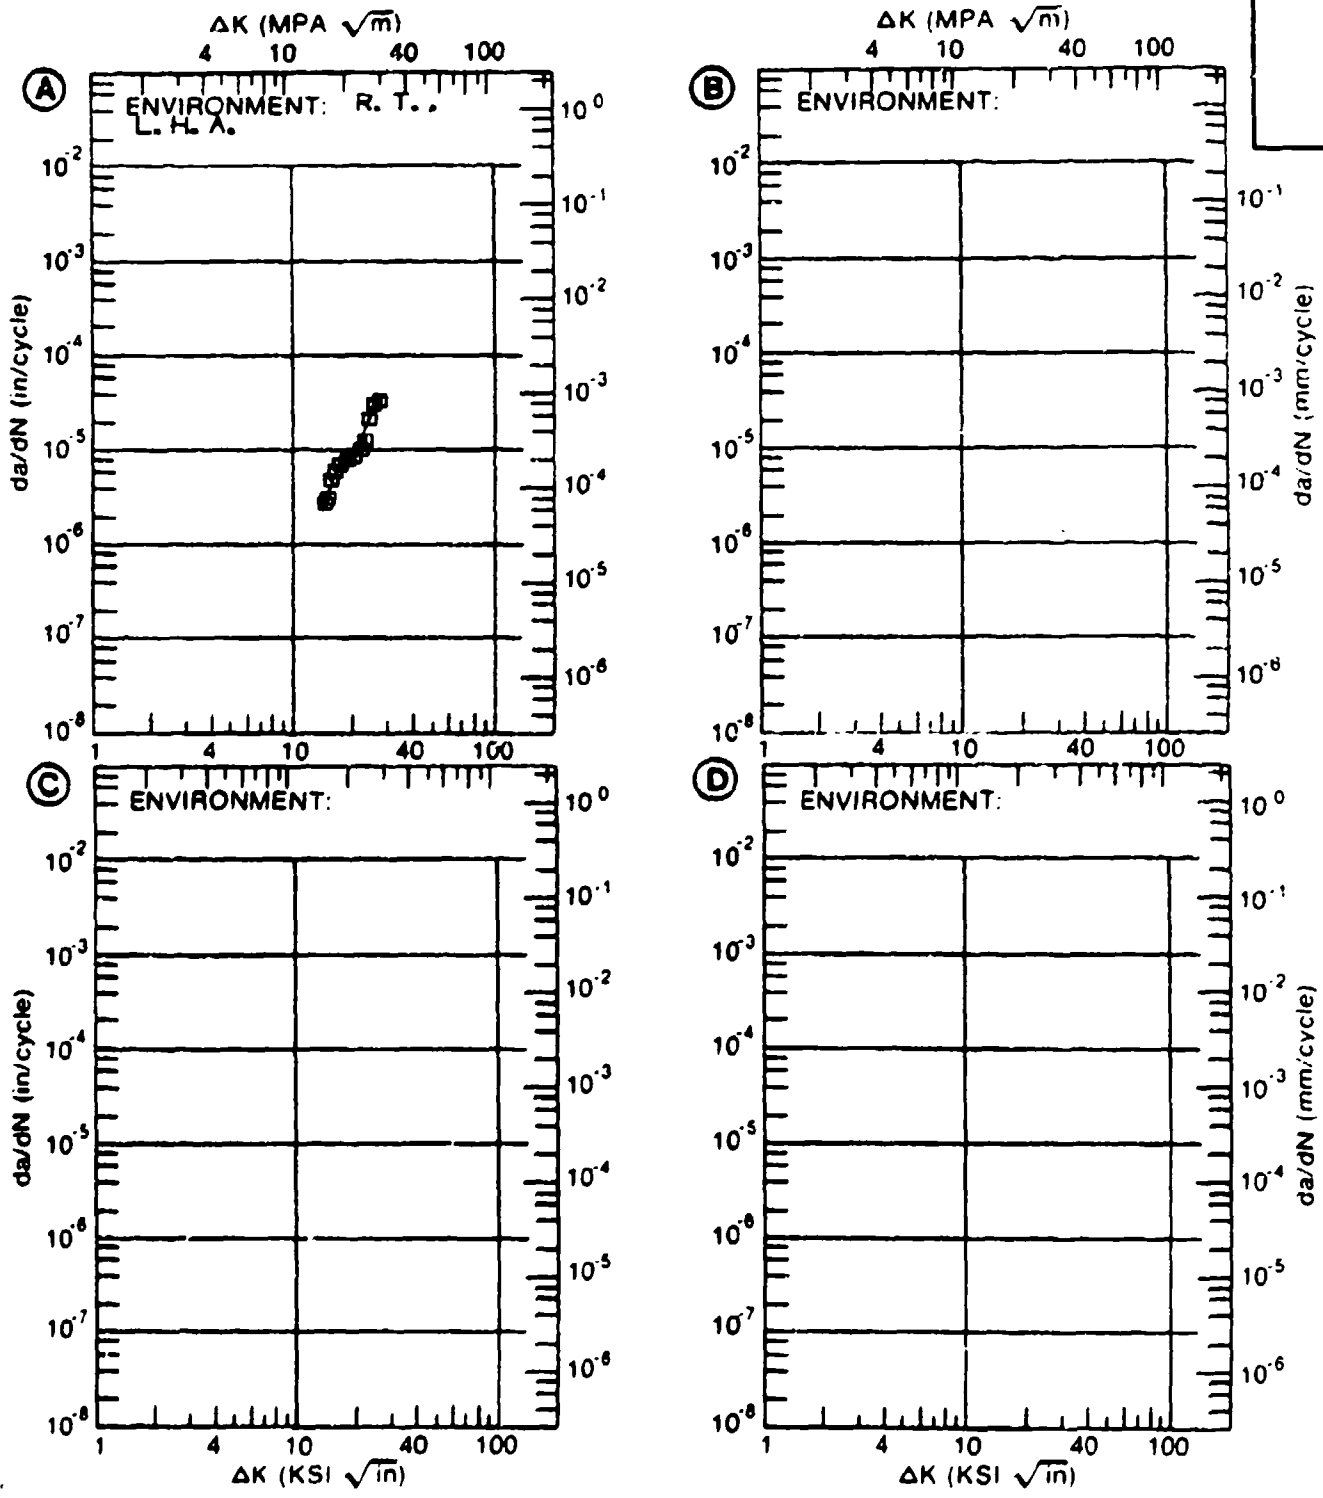


Figure 4.11.3.34

TABLE 4.11.3.35

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.35 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: DB + 4DBTC

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁵ IN./CYCLE)			
	A	B	C	D
	E= R. T. S. T. W.			
DELTA K A: 11.85	.262			
MIN B:				
C:				
D:				
13.00	.473			
16.00	2.26			
20.00	9.02			
25.00	26.2			
30.00	48.5			
35.00	77.4			
40.00	112.			
50.00	209.			
DELTA K A: 54.46	270.			
B:				
MAX C:				
D:				

ROOT MEAN SQUARE 13.83
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: DB + 4DBTC
 FORM: 0.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 115.0 KSI
 ULT. STRENGTH: 126.0 KSI
 SPECIMEN THK: 0.090"
 SPECIMEN WIDTH: 8.000"
 REFERENCES: 85837

TITAN.
 ALLOY

TI-6AL-
 4V

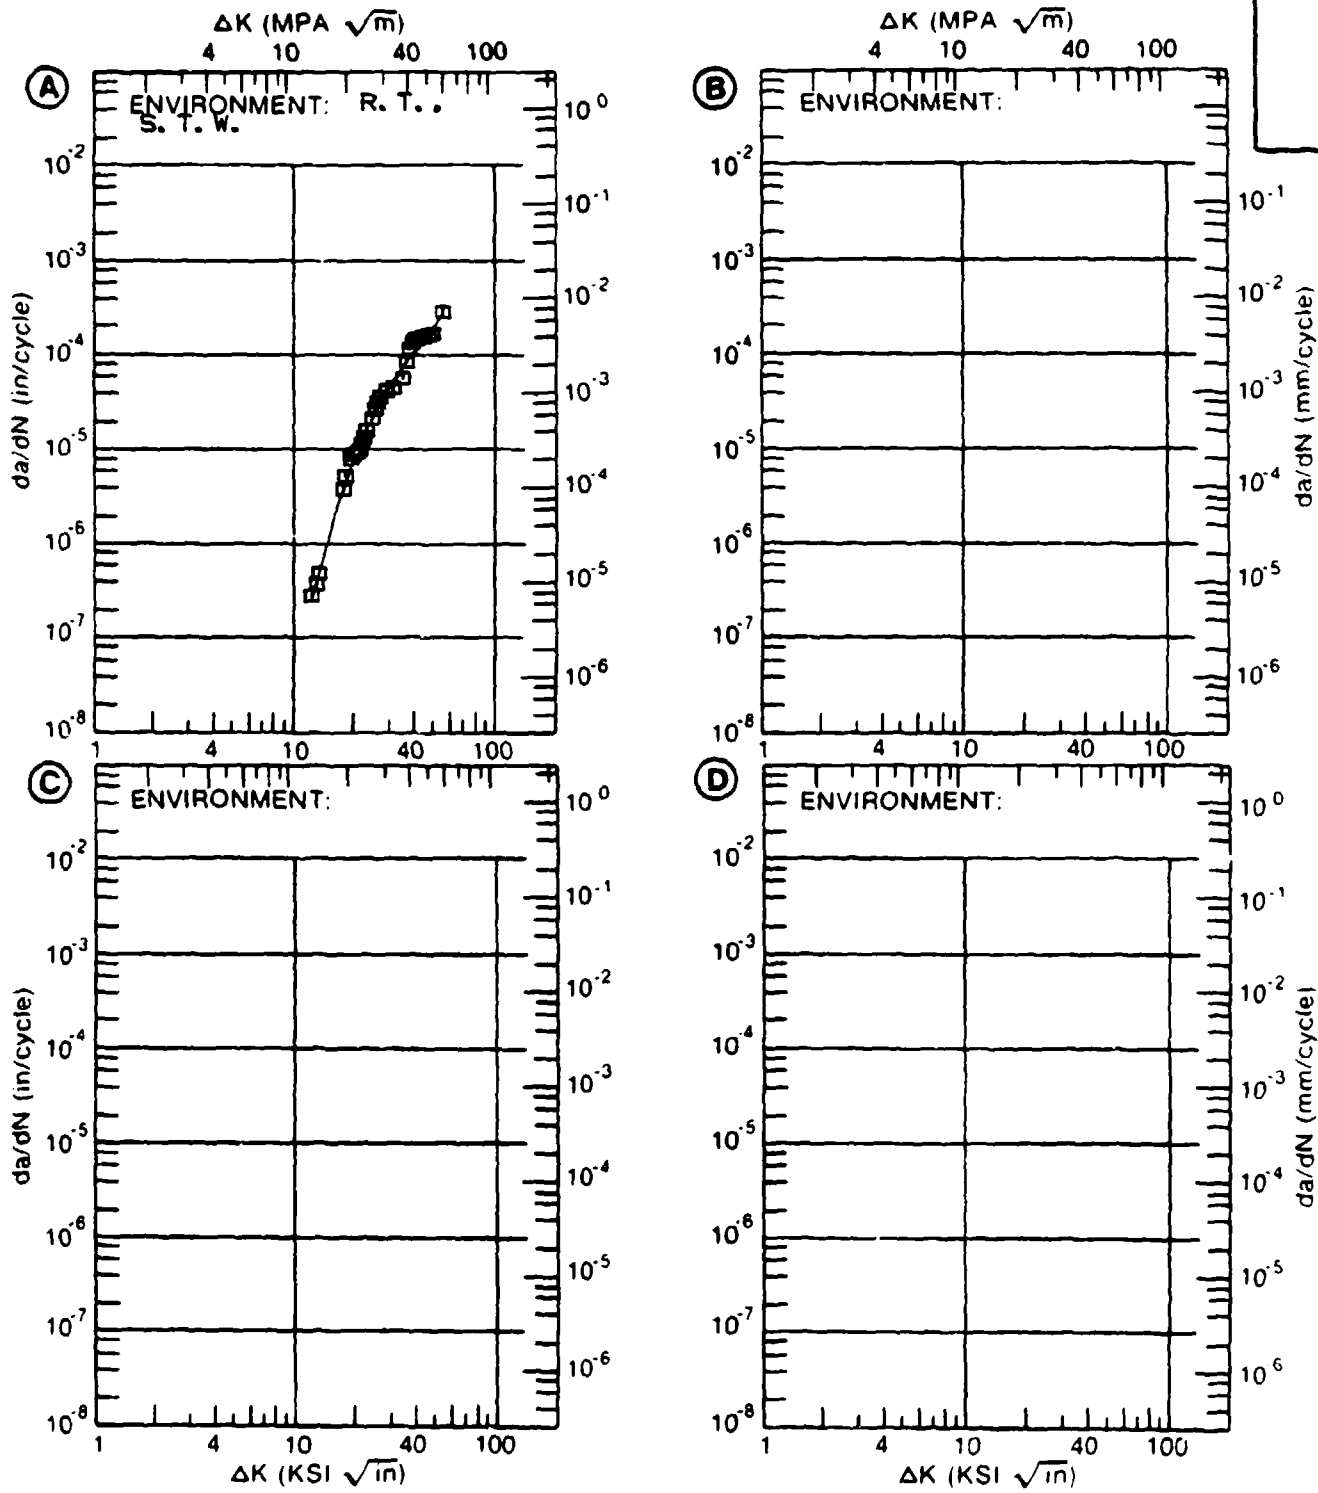


Figure 4.11.3.35

TABLE 4.11.3.36

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.36 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: DBT + PC					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. S. T. W.			
DELTA K MIN	A: 10.37	.256			
	B:				
	C:				
	D:				
	13.00	.631			
	16.00	1.82			
	20.00	11.2			
	25.00	30.5			
DELTA K MAX	A: 27.18	41.3			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		24.25			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: DBT + PC
 FORM: 2.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 122.0 KSI
 ULT. STRENGTH: 135.0 KSI
 SPECIMEN THK: 0.350"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 98570

TITAN.
 ALLOY
 TI-6AL-
 4V

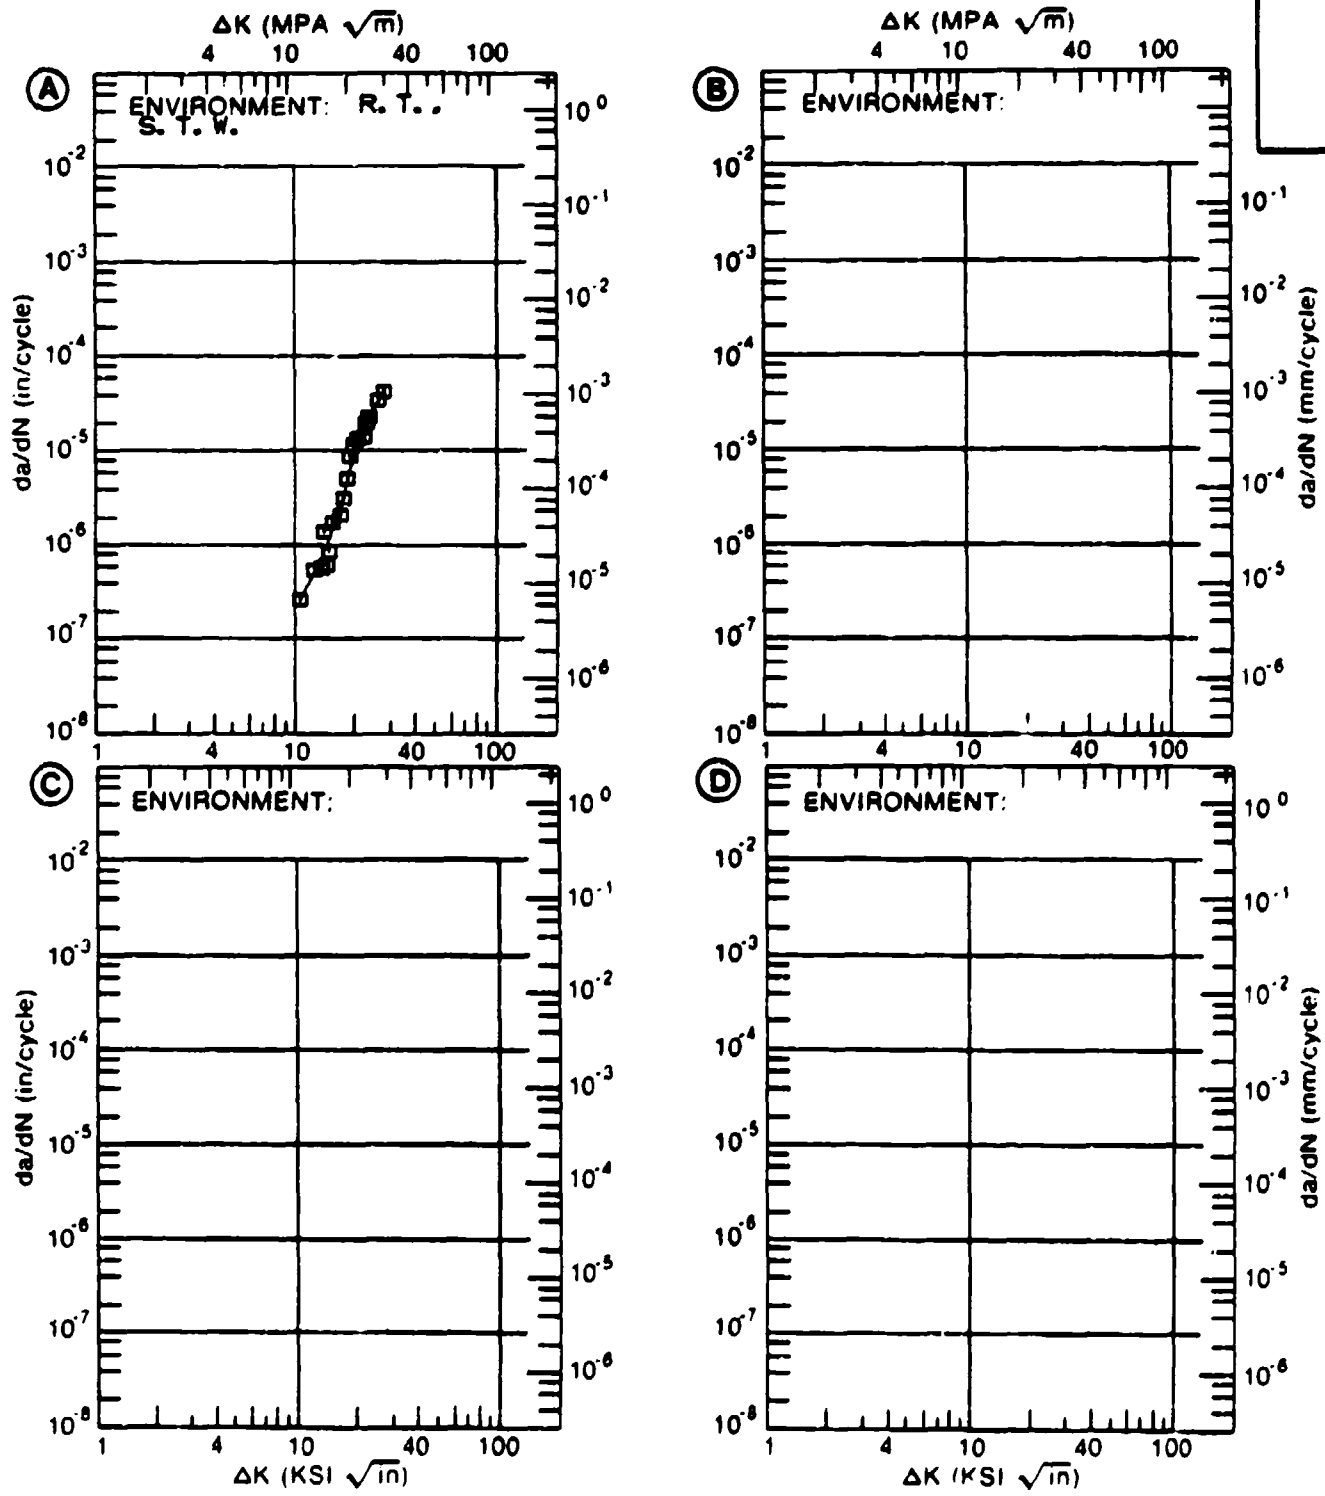


Figure 4.11.3.36

TABLE 4.11.3.37

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.37 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: DBTC					
ENVIRONMENT: R. T. , L. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30		
DELTA K	A: 13.74	3.40			
MIN	B: 9.83		.53		
	C:				
	D:				
	10.00		.626		
	13.00		3.62		
	16.00	8.58	8.93		
	20.00	16.4	19.4		
	25.00	29.4	44.3		
	30.00	51.4	108.		
	35.00	95.1	285.		
	40.00	191.	683.		
	50.00	753.	2181.		
DELTA K	A: 58.30	1802.			
MAX	B: 56.14		4408.		
	C:				
	D:				
ROOT MEAN SQUARE		11.57	11.54		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: DBTC
 FORM: 0.62- 0.63" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 138.0- 140.0 KSI
 ULT. STRENGTH: 148.0- 150.0 KSI
 SPECIMEN THK: 0.496- 0.500"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 88579, 85837

TITAN.
 ALLOY

TI-6AL-
 4V

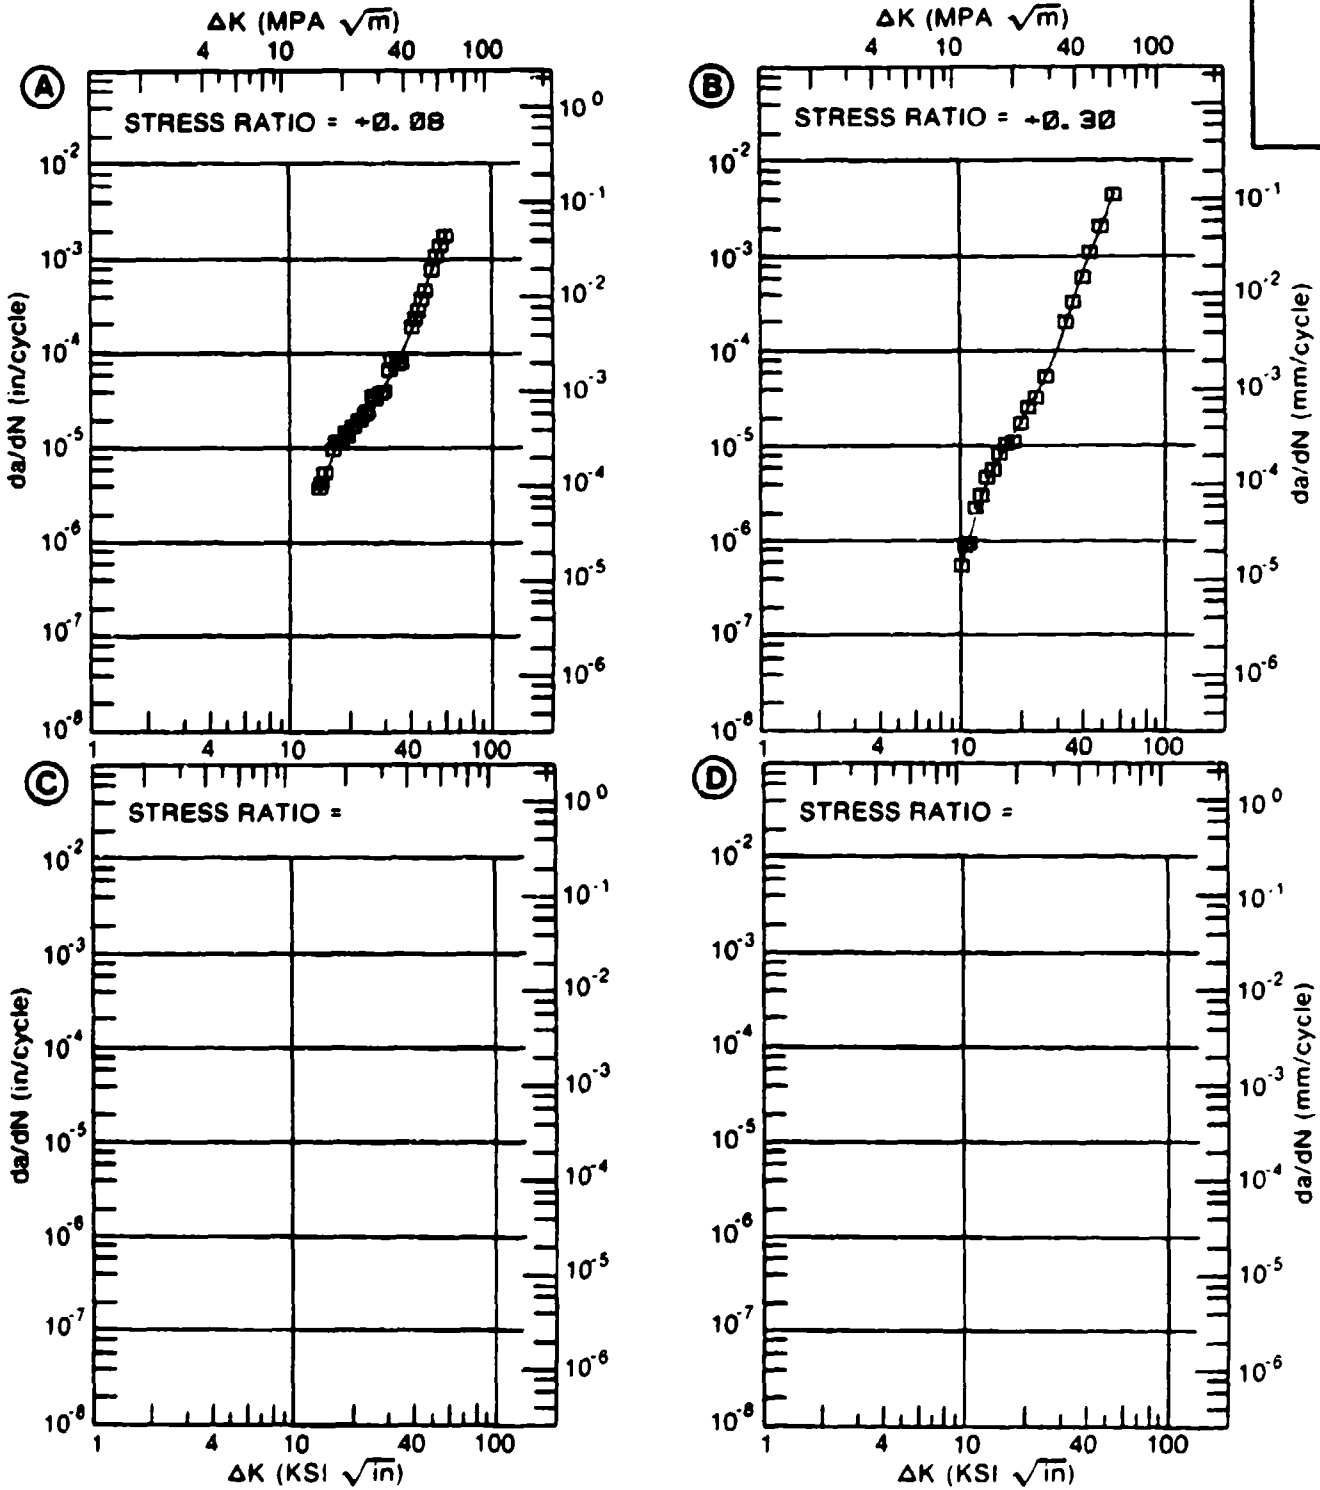


Figure 4.11.3.37

TABLE 4.11.3.38

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.38 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: DBTC					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. S. T. W.		
DELTA K MIN	A: 10.00	.359			
	B:				
	C:				
	D:				
	13.00	1.30			
	16.00	4.77			
	20.00	13.1			
	25.00	26.2			
	30.00	43.1			
	35.00	69.0			
	40.00	110.			
	50.00	285.			
DELTA K MAX	A: 59.95	750.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		29.28	0.00		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: DBTC
 FORM: 1.25" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.30
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 125.0 KSI
 ULT. STRENGTH: 137.0 KSI
 SPECIMEN THK: 0.000 - 1.000"
 SPECIMEN WIDTH: 8.000"
 REFERENCES: 88578, 85837

TITAN.
 ALLOY

TI-6AL-
 4V

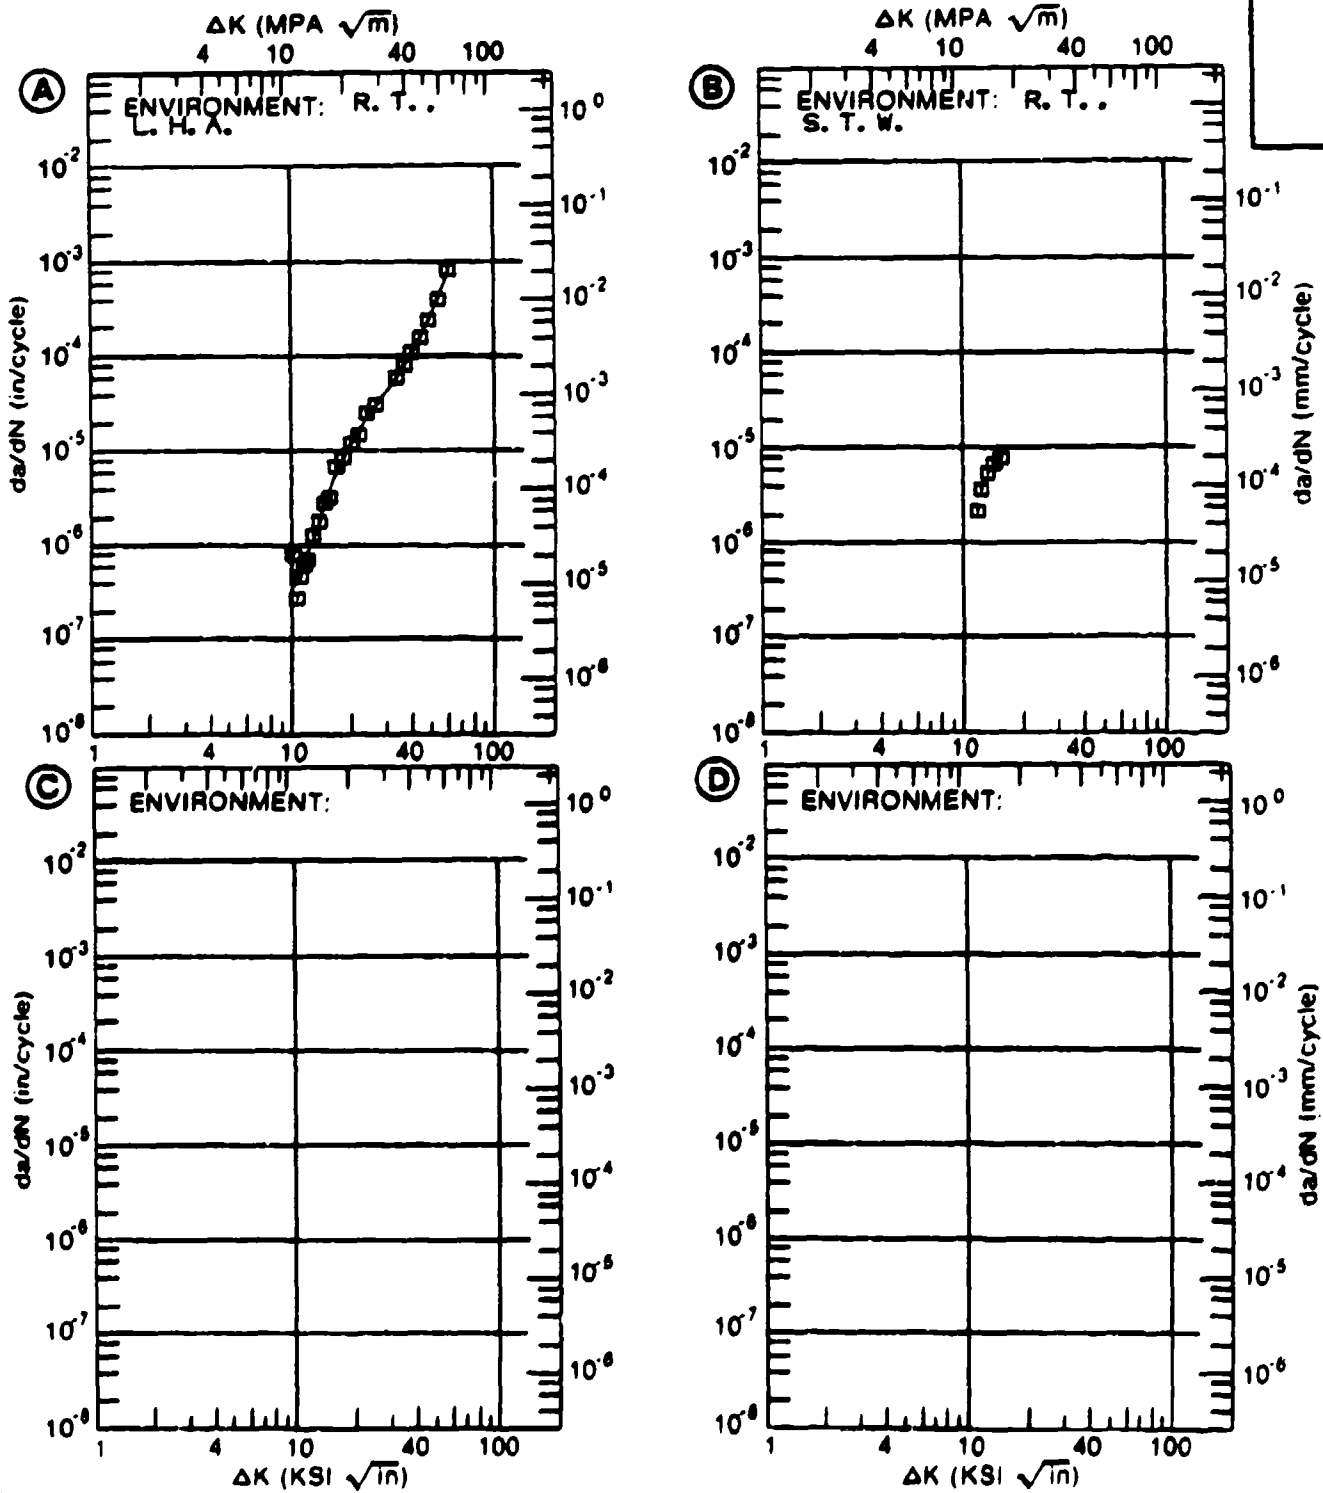


Figure 4.11.3.38

TABLE 4.11.3.39

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.39 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: DBTC

TI-6AL-4V

DELTA K (KBI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E= R. T. L. H. A.			
DELTA K MIN	A: 9.82	.564		
	10.00	.567		
	13.00	1.45		
	16.00	4.82		
	20.00	12.5		
	25.00	24.0		
	30.00	41.1		
	35.00	69.5		
	40.00	114.		
	50.00	278.		
DELTA K MAX	A: 56.48	685.		
ROOT MEAN SQUARE	14.29			
PERCENT ERROR				

LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5	0.5-0.8	0.8-1.25	1	1.25-2.0	>2.0
---------------------------------------	---------	---------	----------	---	----------	------

CONDITION/HT: DBTC
 FORM: 1.25" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.30
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 128.0 KSI
 ULT. STRENGTH: 138.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 8.000"
 REFERENCES: 98570

TITAN.
 ALLOY

TI-6AL-
 4V

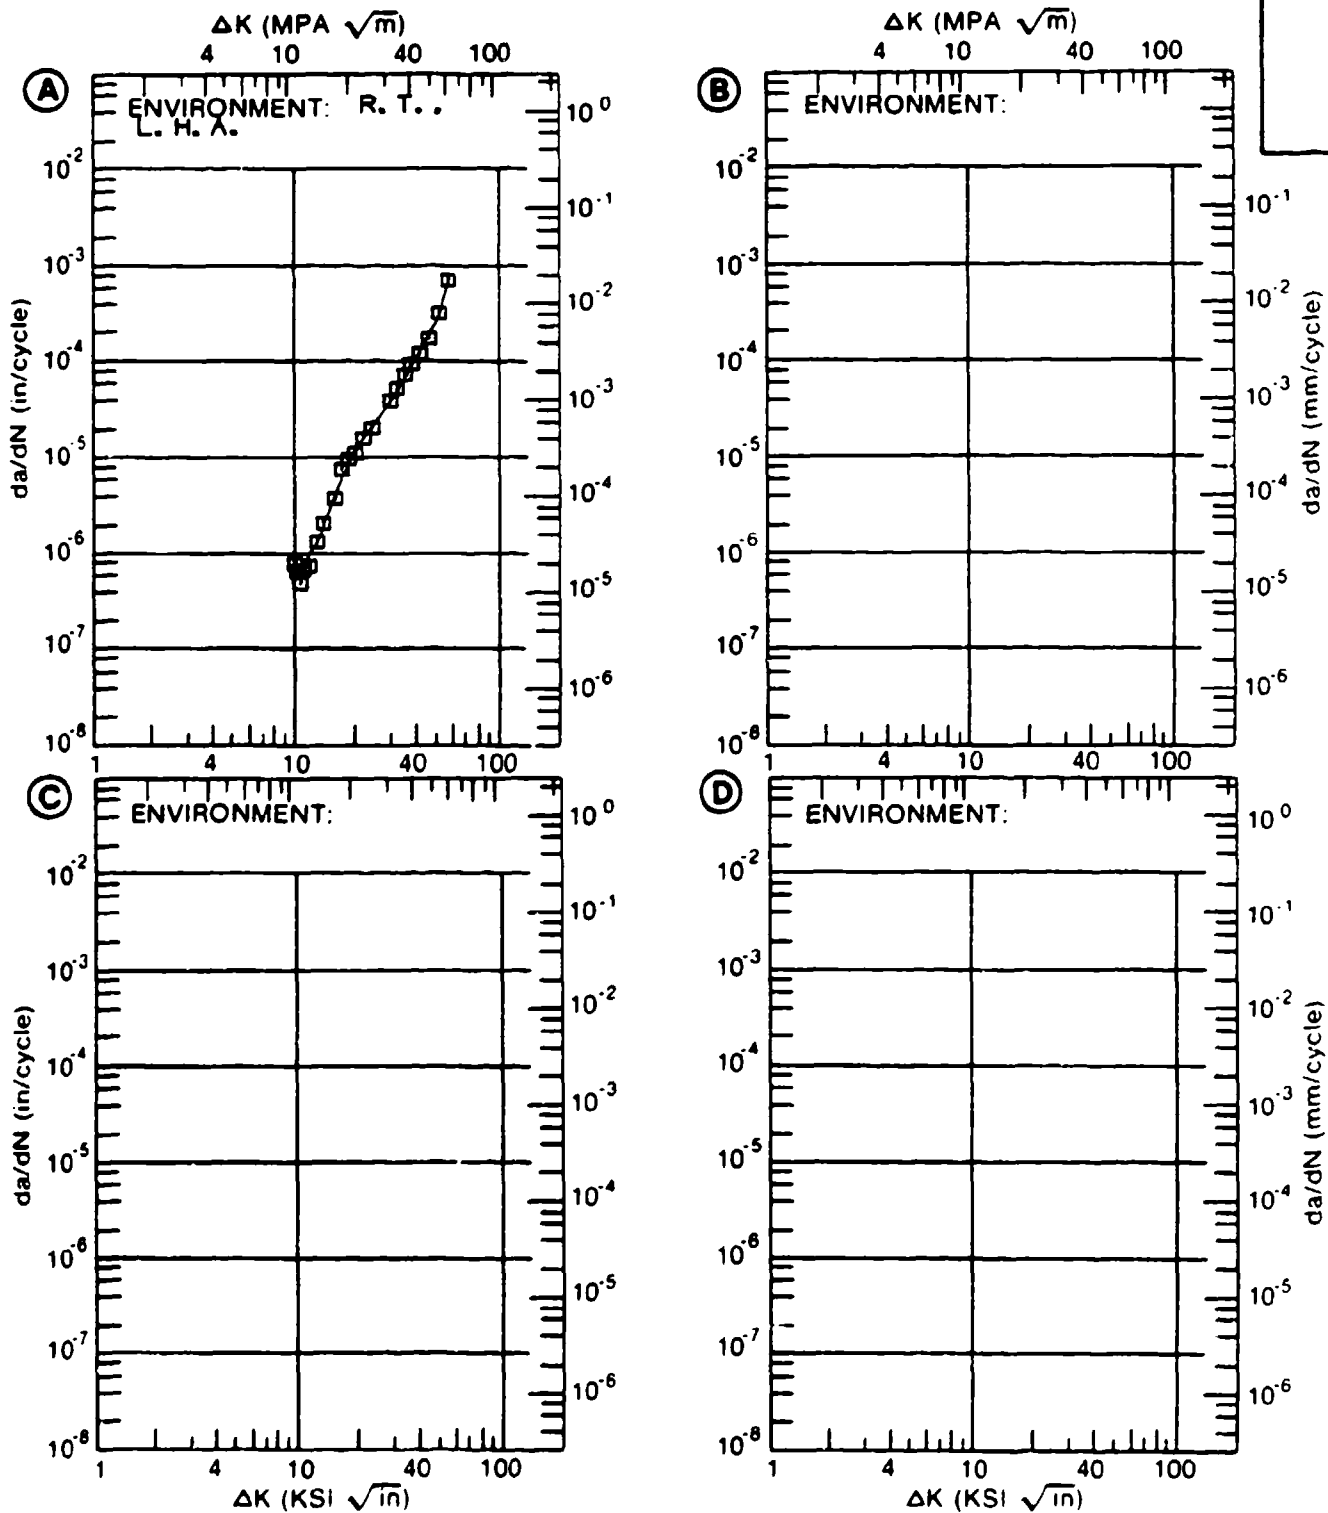


Figure 4.11.3.39

TABLE 4.11.3.40

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.40 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: DBTC					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		S. T. W.			
DELTA K	A: 6.24	.115			
MIN	B:				
	C:				
	D:				
	7.00	.122			
	8.00	.192			
	9.00	.349			
	10.00	.629			
	13.00	2.52			
	16.00	6.33			
	20.00	13.9			
	25.00	27.4			
	30.00	48.6			
	35.00	84.4			
DELTA K	A: 36.57	100.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		33.64			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2			
SUMMARY	1.25-2.0	1			
(NP/NA)	>2.0				

CONDITION/HT: DBTC
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 117.0 - 124.0 KSI
 ULT. STRENGTH: 129.0 - 138.0 KSI
 SPECIMEN THK: 0.990 - 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 88578, 85837

TITAN.
 ALLOY

TI-6AL-
 4V

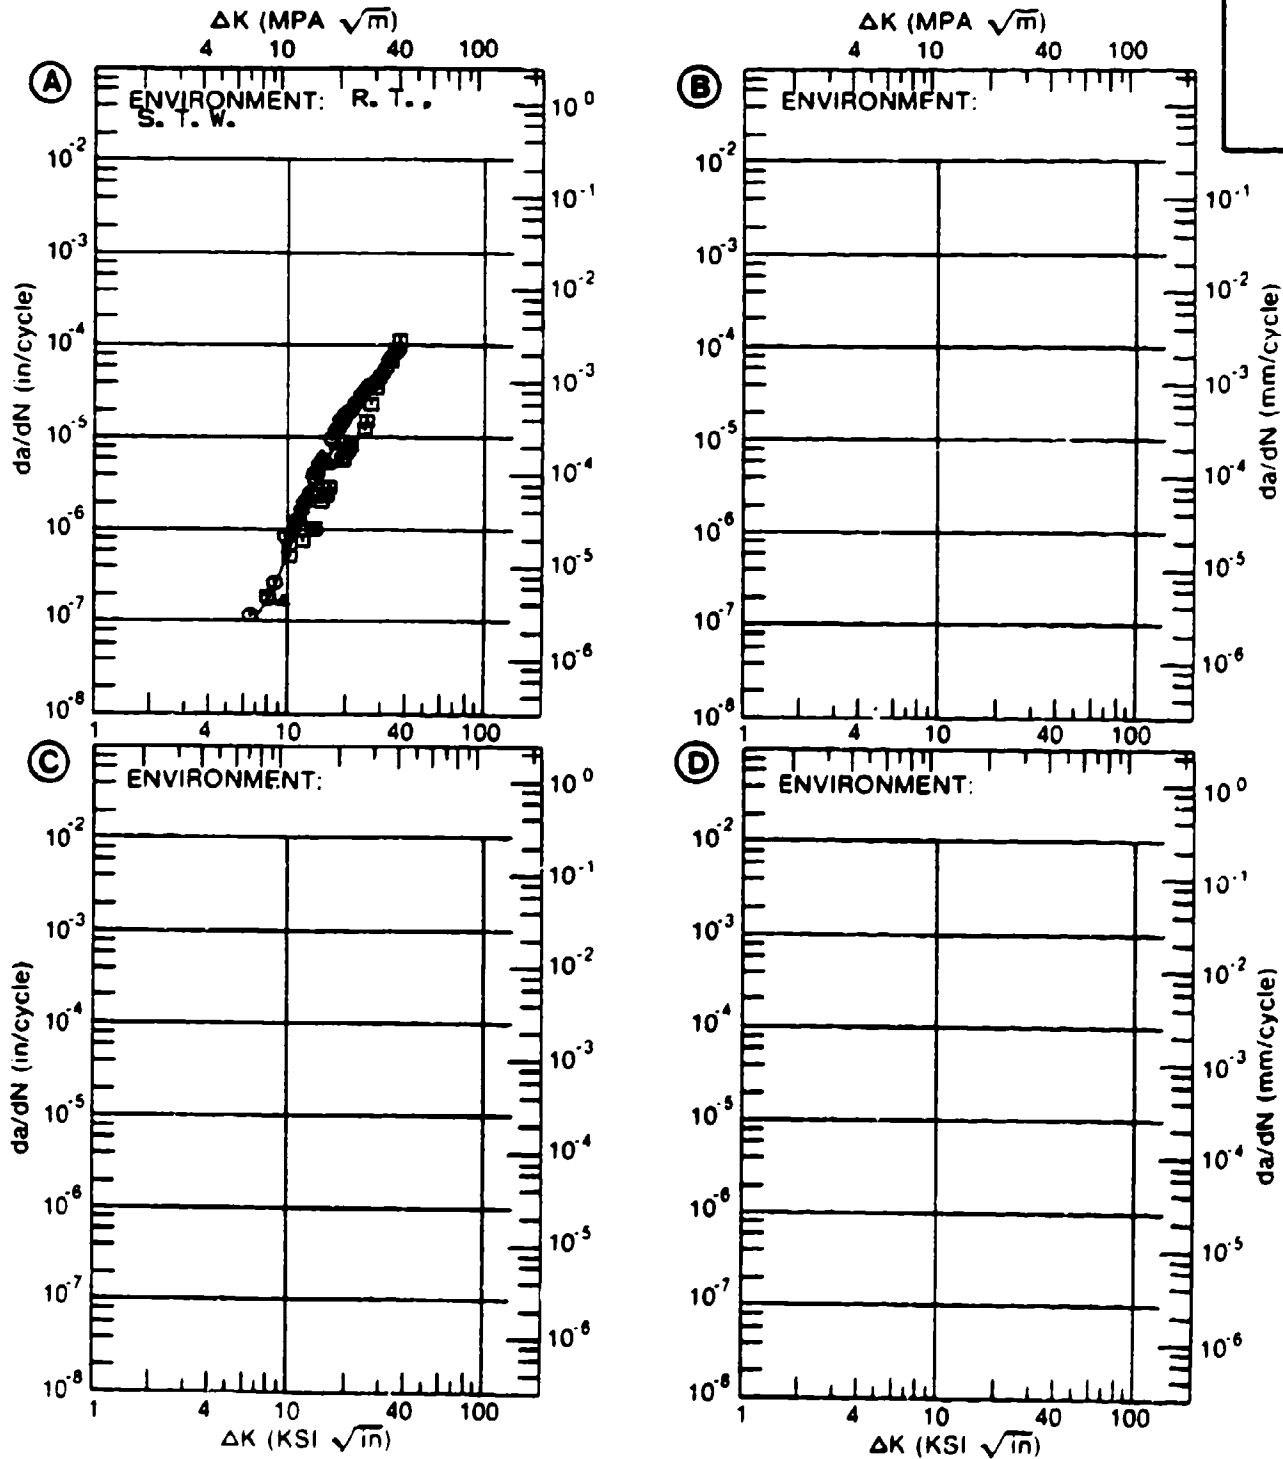


Figure 4.11.3.40

TABLE 4.11.3.41

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.41 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: DBTC					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. B. T. W.		
DELTA K	A: 12.36	.999			
MIN	B: 9.01		1.16		
	C:				
	D:				
	10.00		1.83		
	13.00	1.31	4.86		
	16.00	3.42	9.41		
	20.00	7.70	18.4		
	25.00	15.2	37.3		
	30.00	26.0			
	35.00	41.9			
	40.00	66.5			
	50.00	169.			
DELTA K	A: 57.13	336.			
MAX	B: 29.65		68.3		
	C:				
	D:				
ROOT MEAN SQUARE		8.80	14.34		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	2		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: DBTC
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 118.0- 125.0 KSI
 ULT. STRENGTH: 134.0- 135.0 KSI
 SPECIMEN THK: 0.960- 0.994"
 SPECIMEN WIDTH: 7.390- 7.460"
 REFERENCES: 88578, 85837

TITAN.
 ALLOY

TI-6AL-
 4V

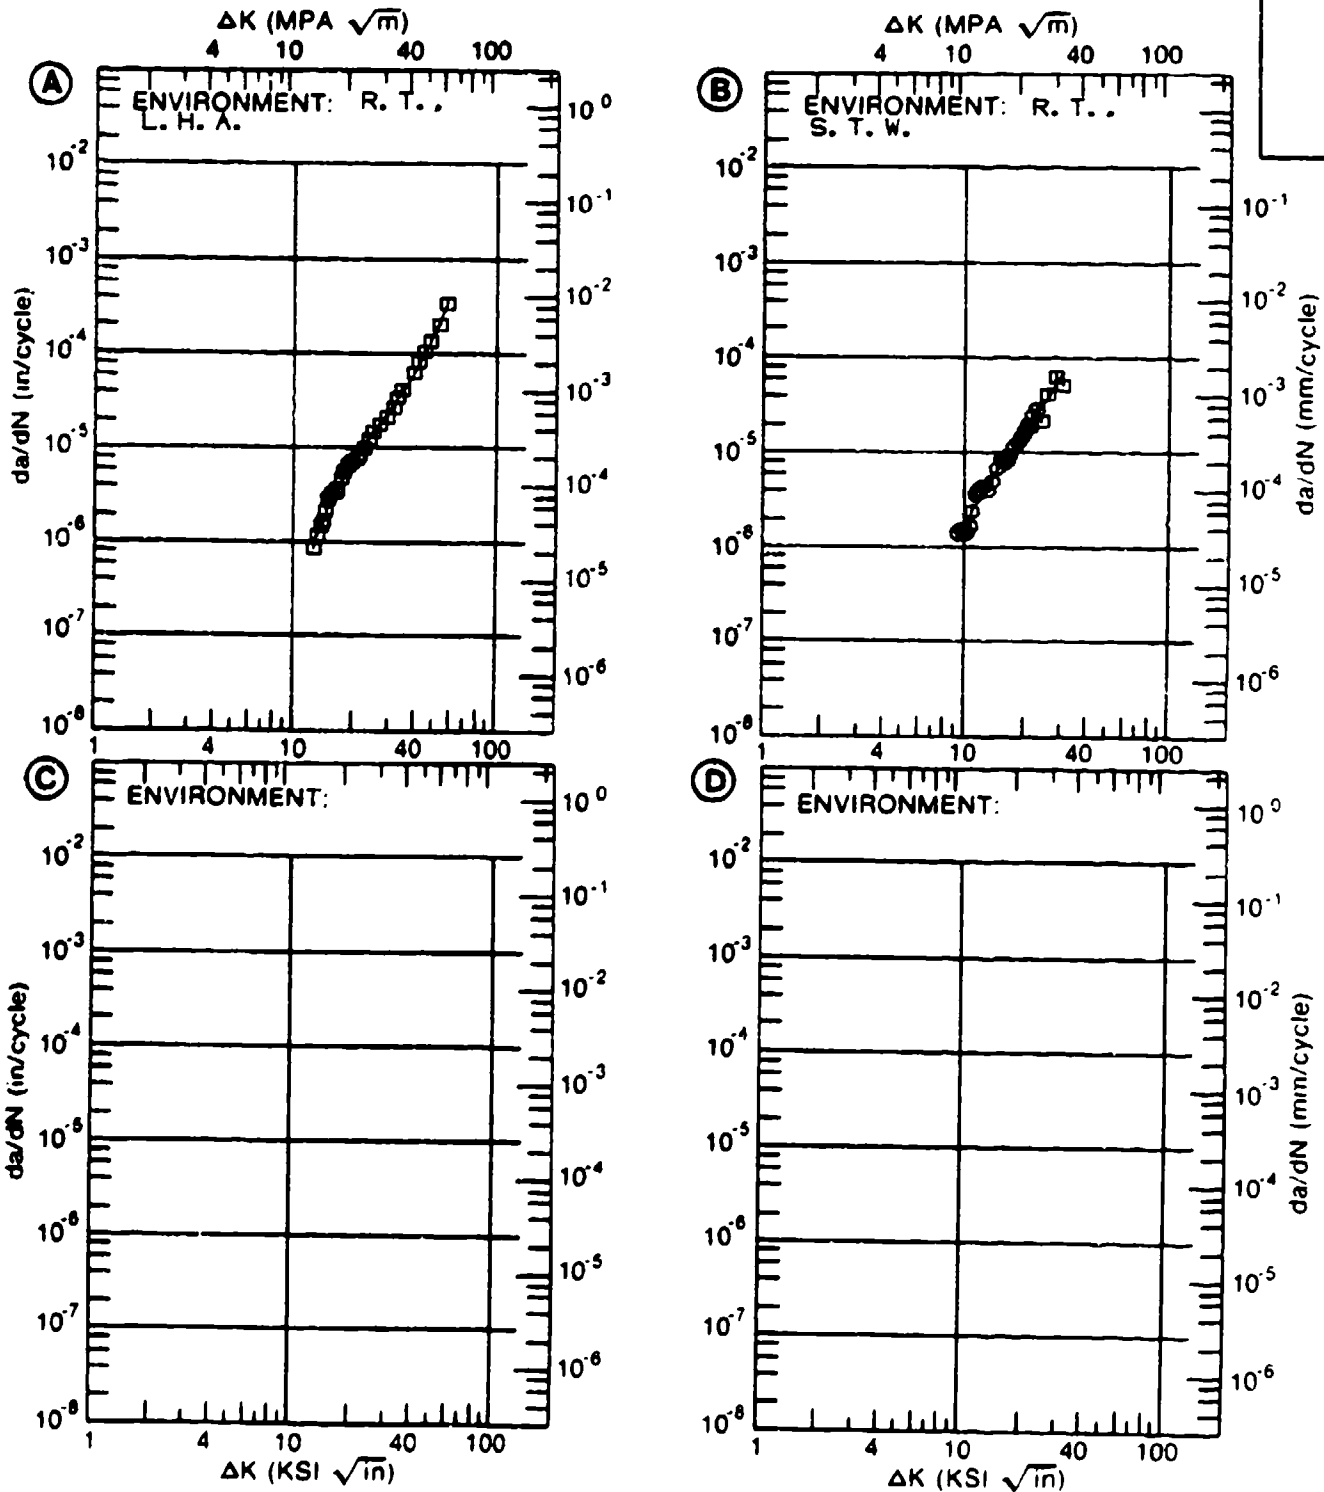


Figure 4.11.3.41

TABLE 4.11.3.42

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.42 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: DBTC					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. STW/JP4			
DELTA K MIN	A: 9.95	.448			
	B:				
	C:				
	D:				
	10.00	.450			
	13.00	.892			
16.00	2.13				
20.00	5.48				
25.00	14.0				
30.00	27.0				
DELTA K MAX	A: 32.61	33.8			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		9.81			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: DBTC
 FORM: 2.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 119.0 KSI
 ULT. STRENGTH: 132.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 4.940"
 REFERENCES: 88579

TITAN.
 ALLOY
 TI-6AL-
 4V

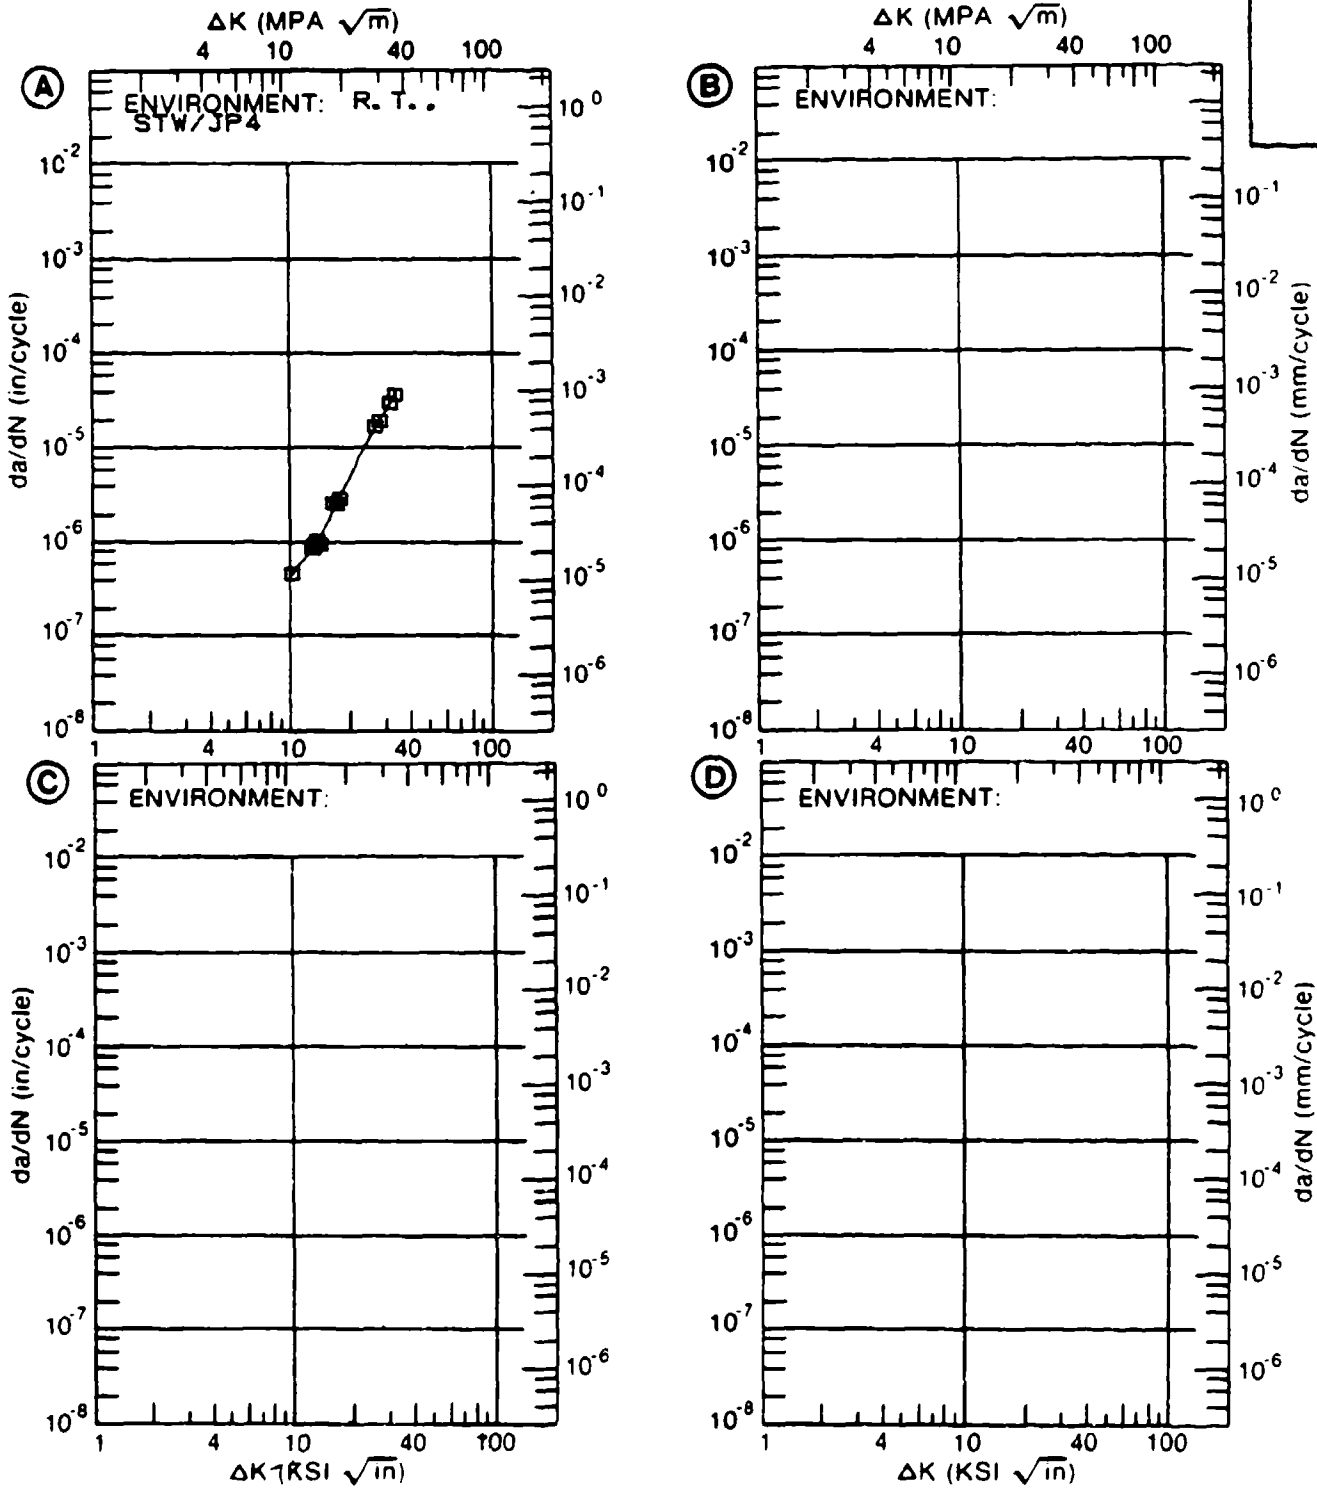


Figure 4.11.3.42

TABLE 4.11.3.43

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.43 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: DBTC(RA)
ENVIRONMENT: R. T. , L. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.30			
DELTA K	A: 30.88	57.1			
MIN	B:				
	C:				
	D:				
	35.00	116.			
	40.00	182.			
DELTA K	A: 40.98	198.			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 13.89
PERCENT ERROR

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	
RATIO	0.8-1.25	1
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: DBTC (RA)
 FORM: 0.63" TH FLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 134.0 KSI
 ULT. STRENGTH: 145.0 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 86579

TITAN.
 ALLOY

TI-6AL-
 4V

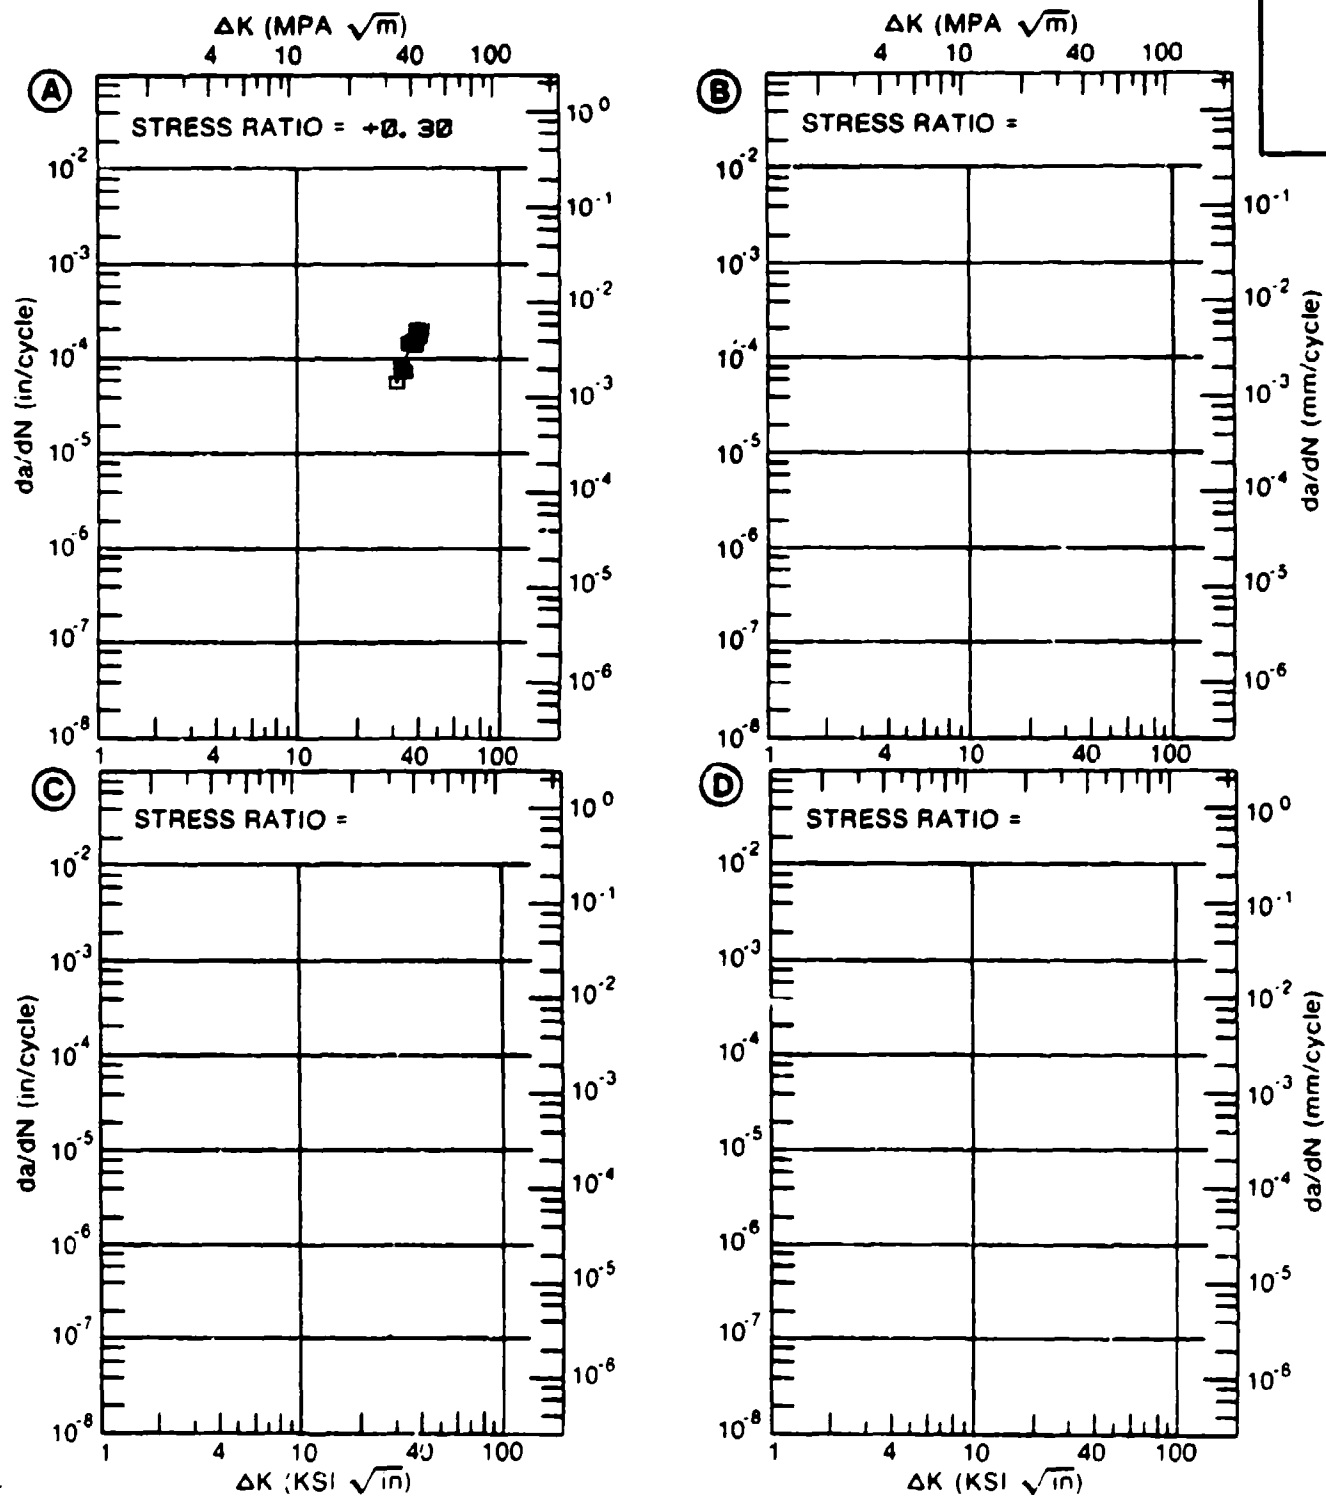


Figure 4.11.3.43

TABLE 4.11.3.44

**FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR**

DATA ASSOCIATED WITH FIGURE 4.11.3.44 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: TITANIUM

TI-6AL-4V

CONDITION: MA

ENVIRONMENT: R. T. , L. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30	R=+0.50	
A: 7.65		.624			
DELTA K B: 6.62			.529		
MIN C: 8.06				.930	
D:					
7.00			.504		
8.00		.755	.790		
9.00		1.21	1.44	1.53	
10.00		1.79	2.24	2.30	
13.00		4.27	4.98	5.34	
16.00		7.75	7.91	9.87	
20.00		13.7		21.1	
25.00		23.2			
30.00		34.8			
A: 30.60		36.4			
DELTA K B: 17.28			9.32		
MAX C: 20.31				22.4	
D:					
ROOT MEAN SQUARE		12.56	13.85	4.35	
PERCENT ERROR					

LIFE 0.0-0.5
 PREDICTION 0.5-0.8
 RATIO 0.8-1.25 2 1 1
 SUMMARY 1.25-2.0
 (NP/NA) >2.0

CONDITION/HT: MA
 FORM: 0.10" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 137.0 KSI
 ULT. STRENGTH: 147.0 KSI
 SPECIMEN THK. 0.093- 0.101"
 SPECIMEN WIDTH: 23.980- 24.220"
 REFERENCES 86575

TITAN.
 ALLOY

TI-6AL-
 4V

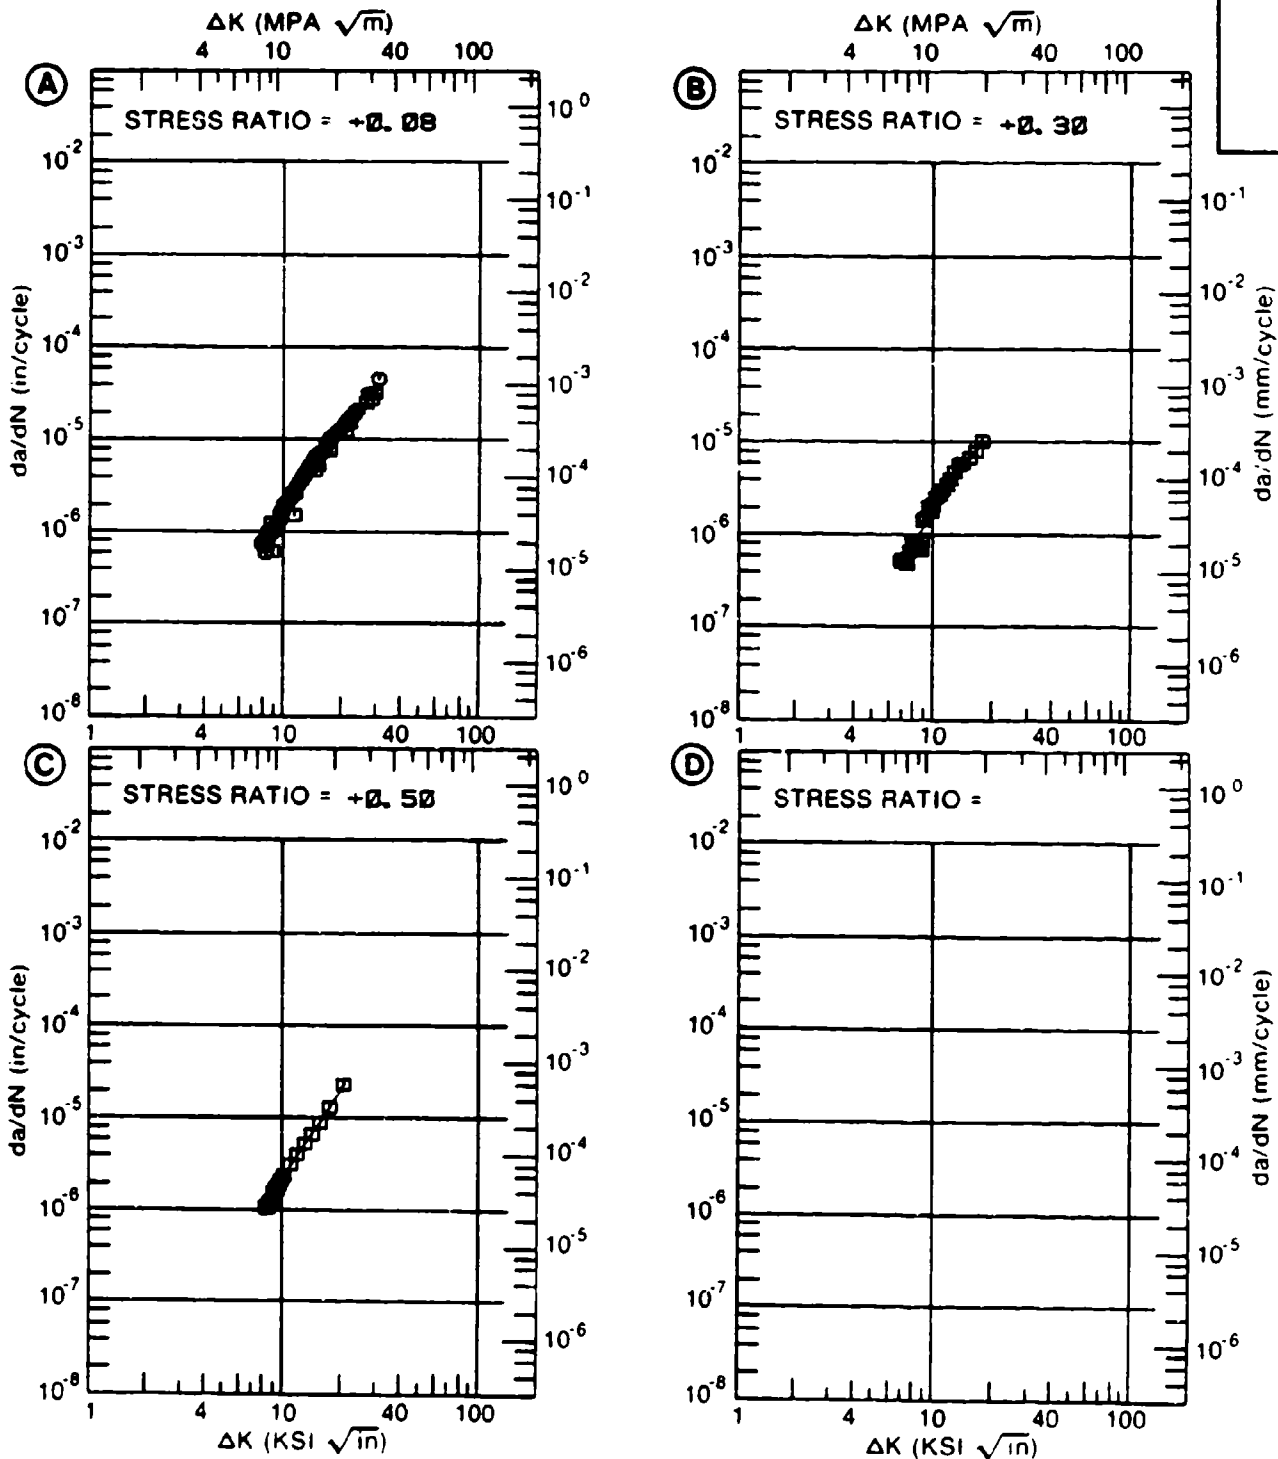


Figure 4.11.3.44

TABLE 4.11.3.45

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.45 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A. 1HZ	E= R. T. JP-4 FUEL 6HZ	E= R. T. S. T. W. 1HZ	
DELTA K	A: 9.64	1.36			
MIN	B: 8.05		1.10		
	C: 5.67			.45	
	D:				
	6.00			.505	
	7.00			.743	
	8.00			1.16	
	9.00		1.23	1.91	
	10.00	1.57	1.47	3.22	
	13.00	4.02	2.88	15.0	
	16.00	7.47	5.82	30.2	
	20.00	12.9	12.9		
	25.00		24.2		
	30.00		30.2		
DELTA K	A: 24.57	19.3			
MAX	B: 30.58		30.3		
	C: 19.01			37.1	
	D:				
ROOT MEAN SQUARE		7.29	21.18	6.77	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1	1	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: 0.10" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 137.0 KSI
 ULT. STRENGTH: 147.0 KSI
 SPECIMEN THK: 0.002- 0.006"
 SPECIMEN WIDTH: 24.000"
 REFERENCES: 00575

TITAN.
 ALLOY

TI-6AL-
 4V

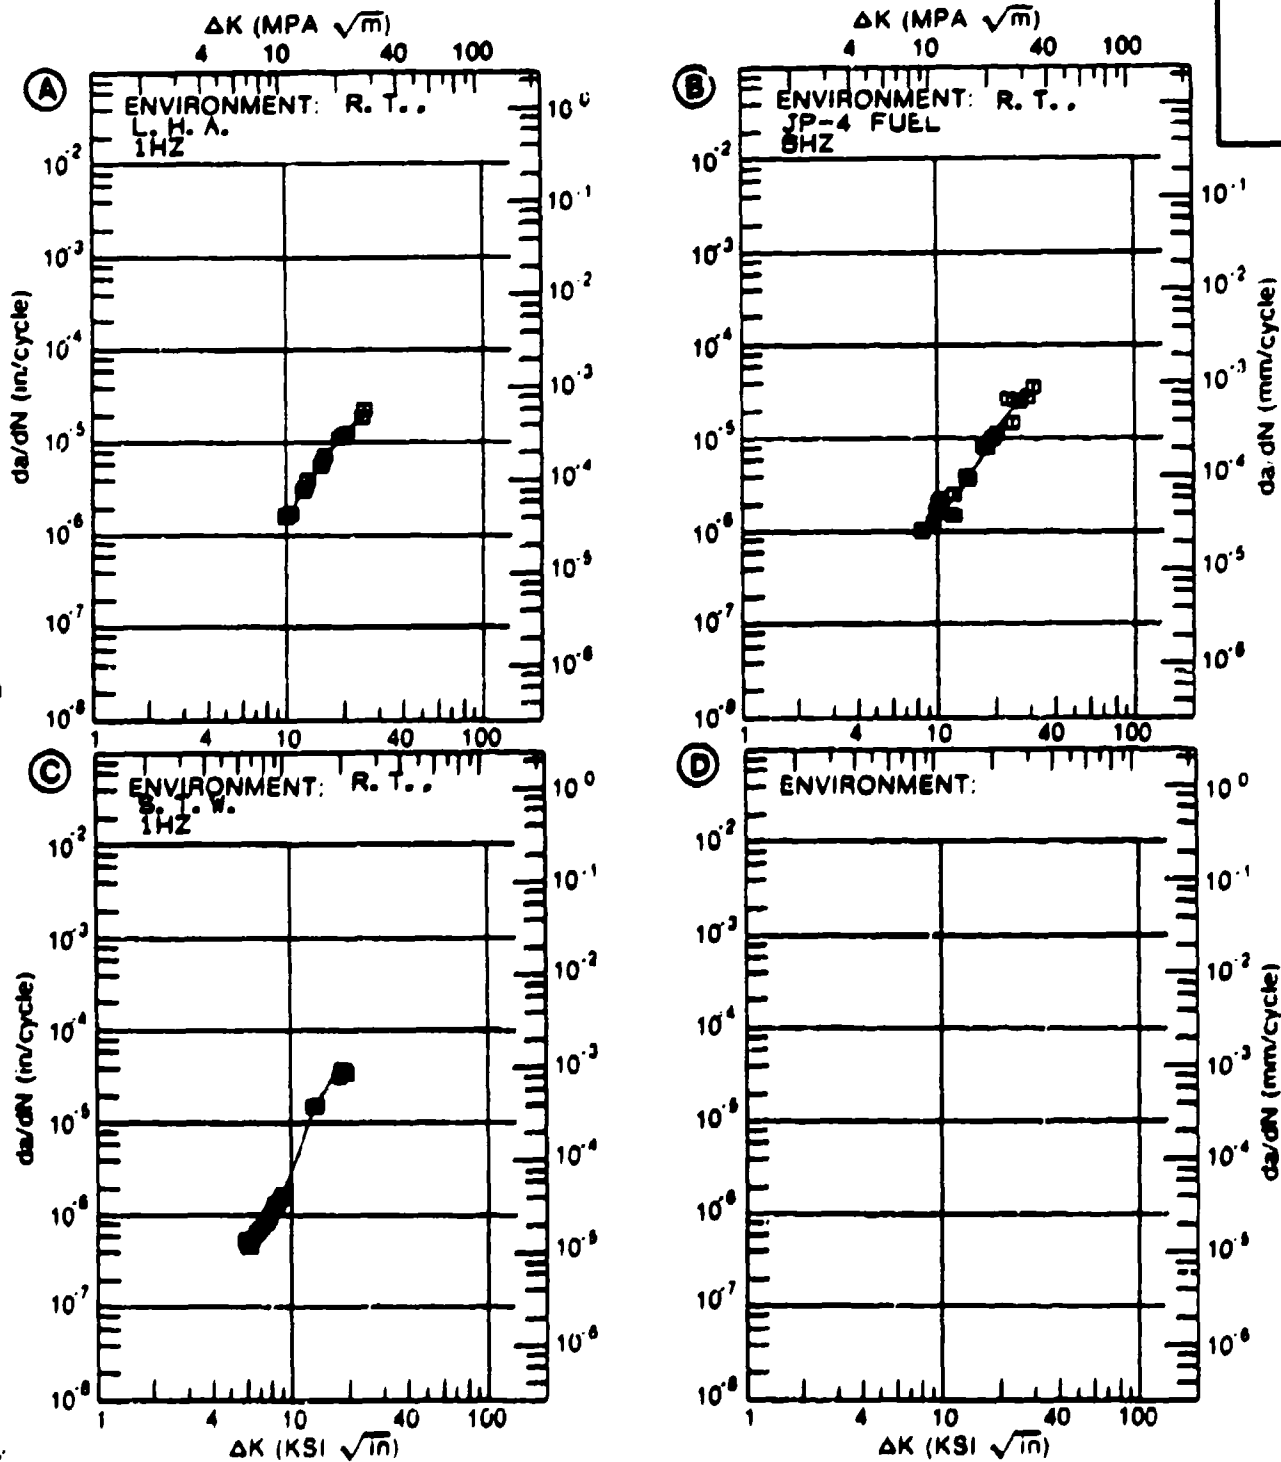


Figure 4.11.3.4b

TABLE 4.11.3.46

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.46 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: MA

TI-6AL-4V

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. S. T. W.		
DELTA K MIN	A: 11.52	2.24			
	B:				
	C:				
	D:				
	13.00	3.06			
	16.00	5.19			
	20.00	9.22			
	25.00	16.7			
	30.00	28.0			
	35.00	44.3			
	40.00	67.5			
DELTA K MAX	A: 44.86	99.0			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		5.77	0.00		
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0		1		

CONDITION/HT: MA
 FORM: 0.10" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 8.00 HZ

YIELD STRENGTH: 143.0 KSI
 ULT. STRENGTH: 151.0 KSI
 SPECIMEN THK: 0.006- 0.007"
 SPECIMEN WIDTH: 24.000"
 REFERENCES: 88575

TITAN.
 ALLOY

TI-6AL-
 4V

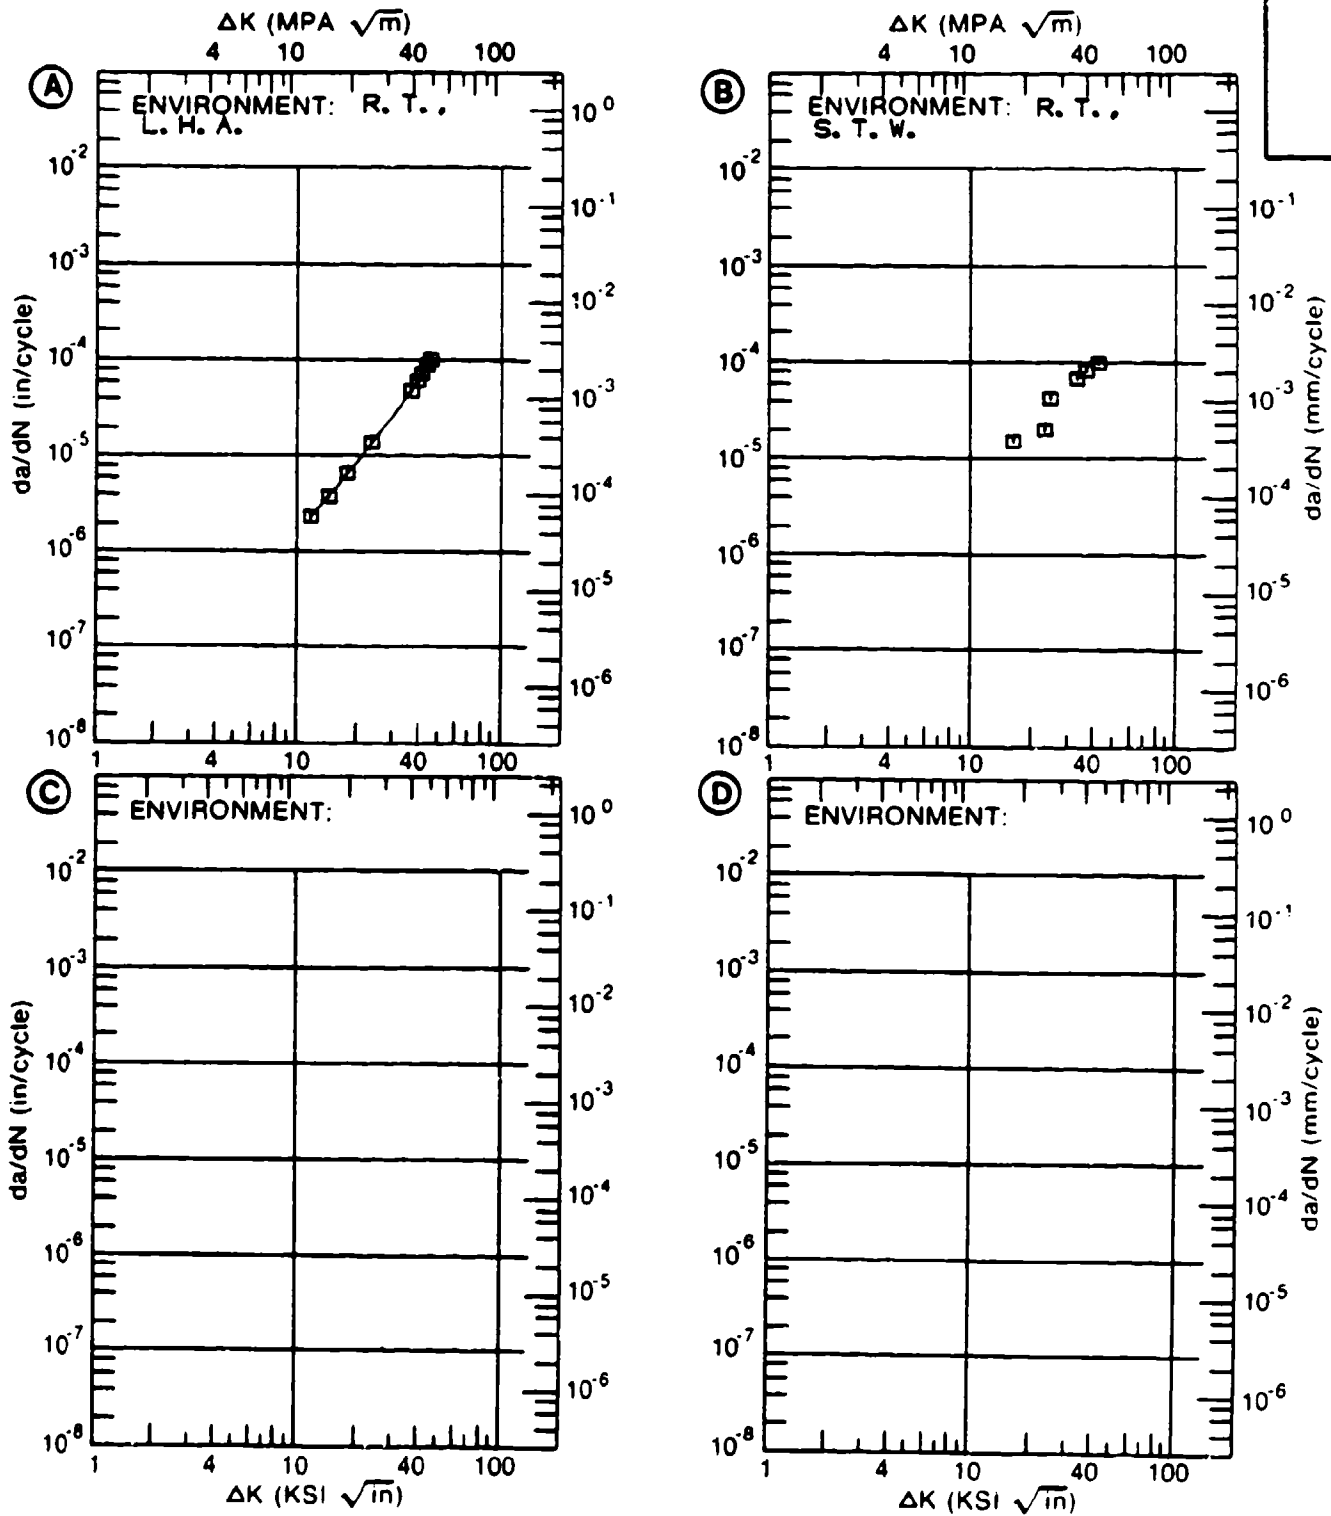


Figure 4.11.3.46

TABLE 4.11.3.47

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.47 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: MA
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.02			
DELTA K	A: 4.82	.0166			
MIN	B:				
	C:				
	D:				
	5.00	.0193			
	6.00	.0414			
	7.00	.0822			
	8.00	.152			
	9.00	.266			
	10.00	.442			
	13.00	1.59			
	16.00	4.34			
	20.00	12.4			
	25.00	33.5			
	30.00	71.4			
	35.00	129.			
DELTA K	A: 38.83	185.			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 27.55
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: MA
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 0.10- 30.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 137.0 KSI
 ULT. STRENGTH: 145.0 KSI
 SPECIMEN THK: 0.241- 0.242"
 SPECIMEN WIDTH: 3.952- 3.953"
 REFERENCES: MA002

TITAN.
 ALLOY
 TI-6AL-
 4V

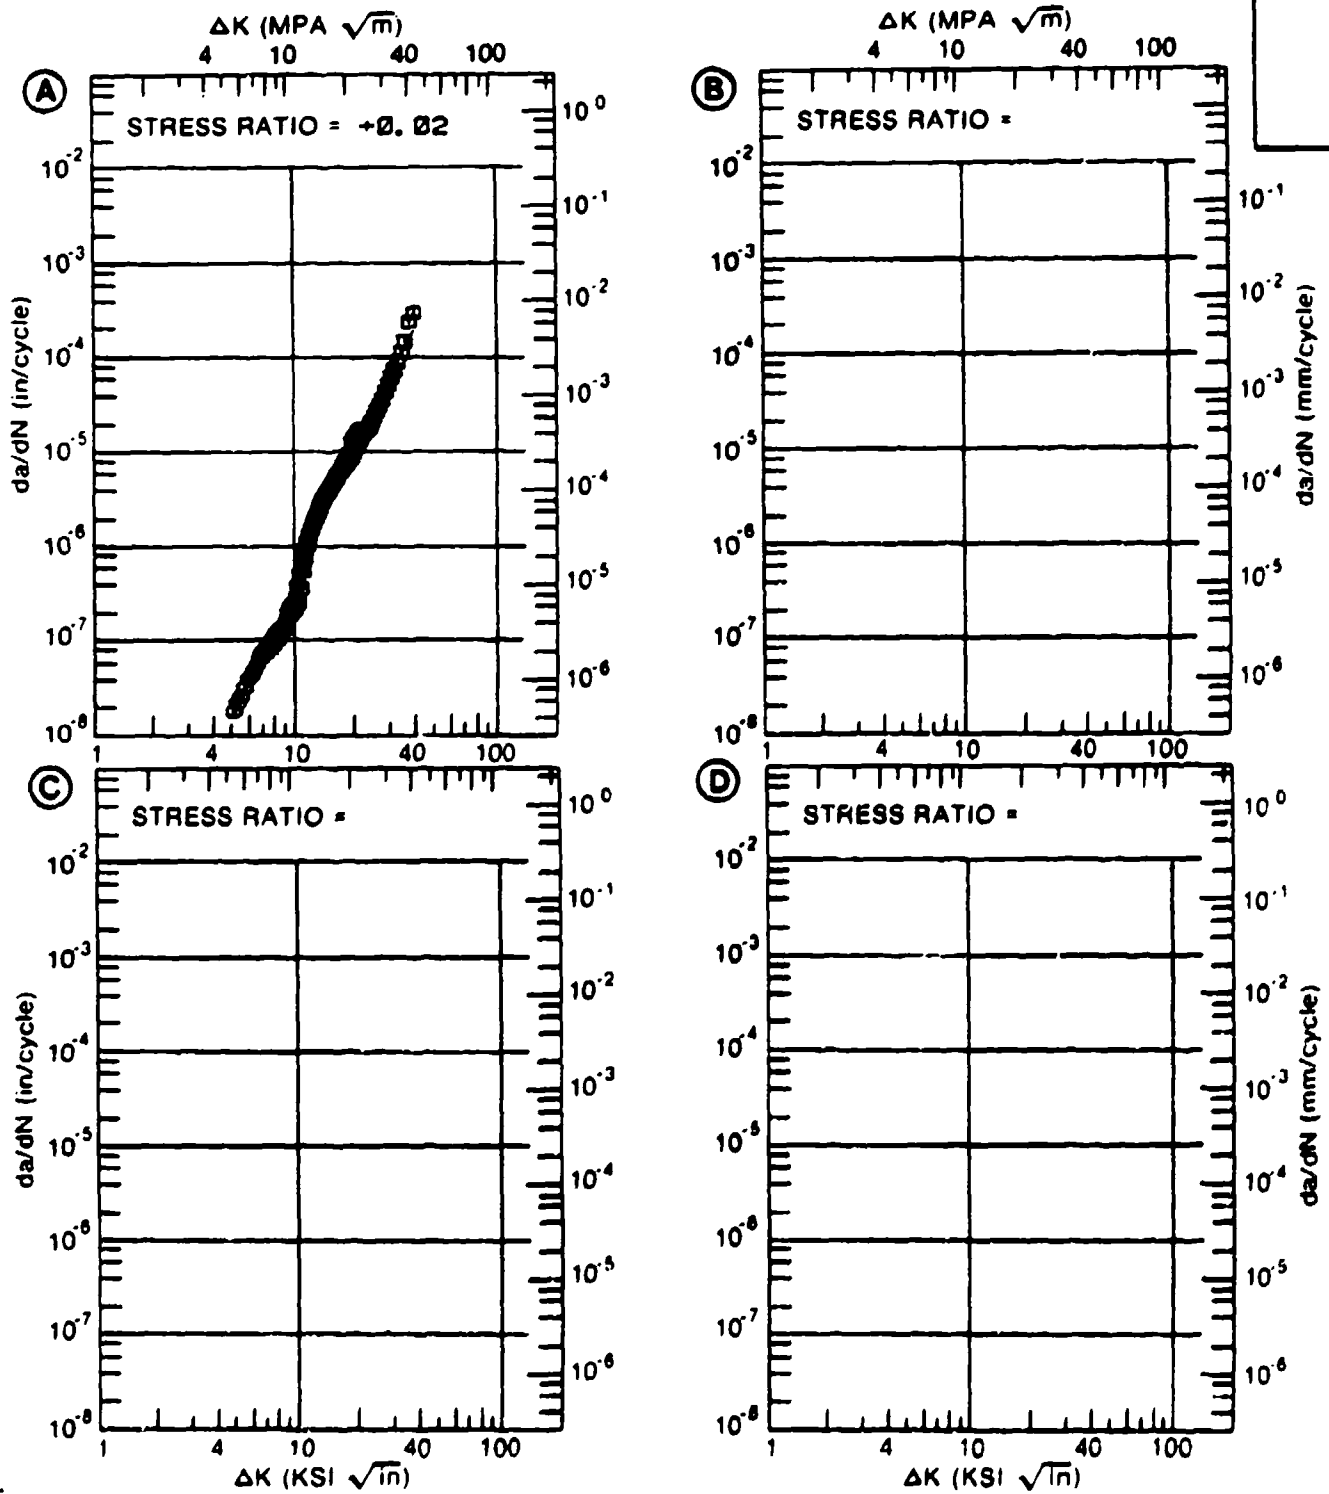


Figure 4.11.3.47

TABLE 4.11.3.48

**FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR**

DATA ASSOCIATED WITH FIGURE 4.11.3.48 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
DELTA K (KBI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A. SP. THK. = . 67"	E= R. T. L. H. A. SP. THK. = . 50"	E= R. T. S. T. W. SP. THK. = . 49"	
DELTA K	A: 26.05	144.			
MIN	B: 11.30		4.69		
	C: 10.36			21.1	
	D:				
	13.00		8.27	33.8	
	16.00		20.4	47.9	
	20.00		72.6	87.5	
	25.00		452.		
	30.00	313.	2284.		
	35.00	679.			
DELTA K	A: 39.74	1469.			
MAX	B: 33.26		3567.		
	C: 23.71			198.	
	D:				
ROOT MEAN SQUARE		7.55	17.55	22.03	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1	1	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: 0.83" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: $\rightarrow 0.30$
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 138.0 KSI
 ULT. STRENGTH: 148.0 KSI
 SPECIMEN THK:
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 88579

TITAN.
 ALLOY

TI-6AL-
 4V

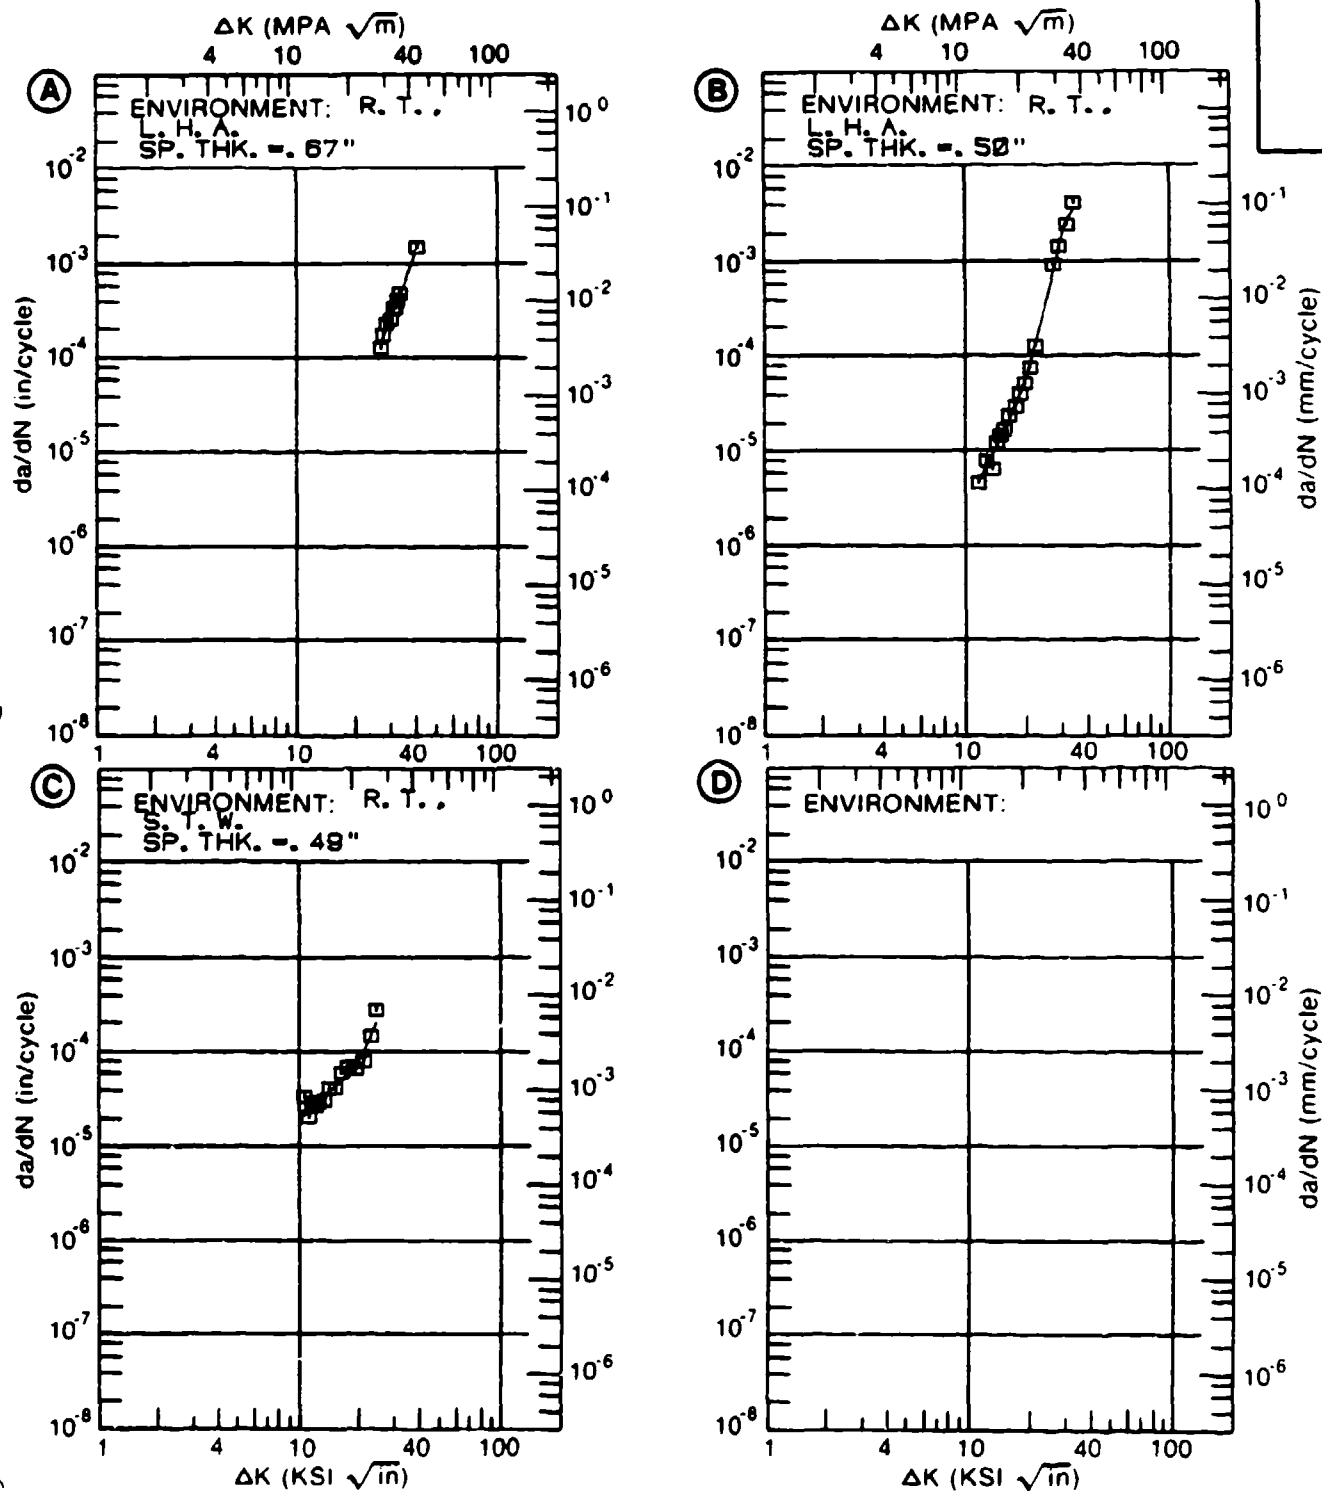


Figure 4.11.3.48

TABLE 4.11.3.49

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.49 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: MA
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.05	R=+0.30		
DELTA K	A: 11.31	.313			
MIN	B: 8.78		.342		
	C:				
	D:				
	9.00		.429		
	10.00		.995		
	13.00	.568	3.46		
	16.00	2.98			
	20.00	6.97			
	25.00	9.80			
	30.00	13.8			
	35.00	25.4			
DELTA K	A: 38.24	45.0			
MAX	B: 14.23		4.08		
	C:				
	D:				
ROOT MEAN SQUARE		24.23	22.40		
PERCENT ERROR					

LIFE	0.0-0.5		
PREDICTION	0.5-0.8		1
RATIO	0.8-1.25	2	
SUMMARY	1.25-2.0		
(NP/NA)	>2.0		

CONDITION/HT: MA
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R.T., LAB AIR

YIELD STRENGTH: 135.3 KSI
 ULT. STRENGTH: 137.6 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 2.500"
 REFERENCES: 88468

TITAN.
 ALLOY
 TI-6AL-
 4V

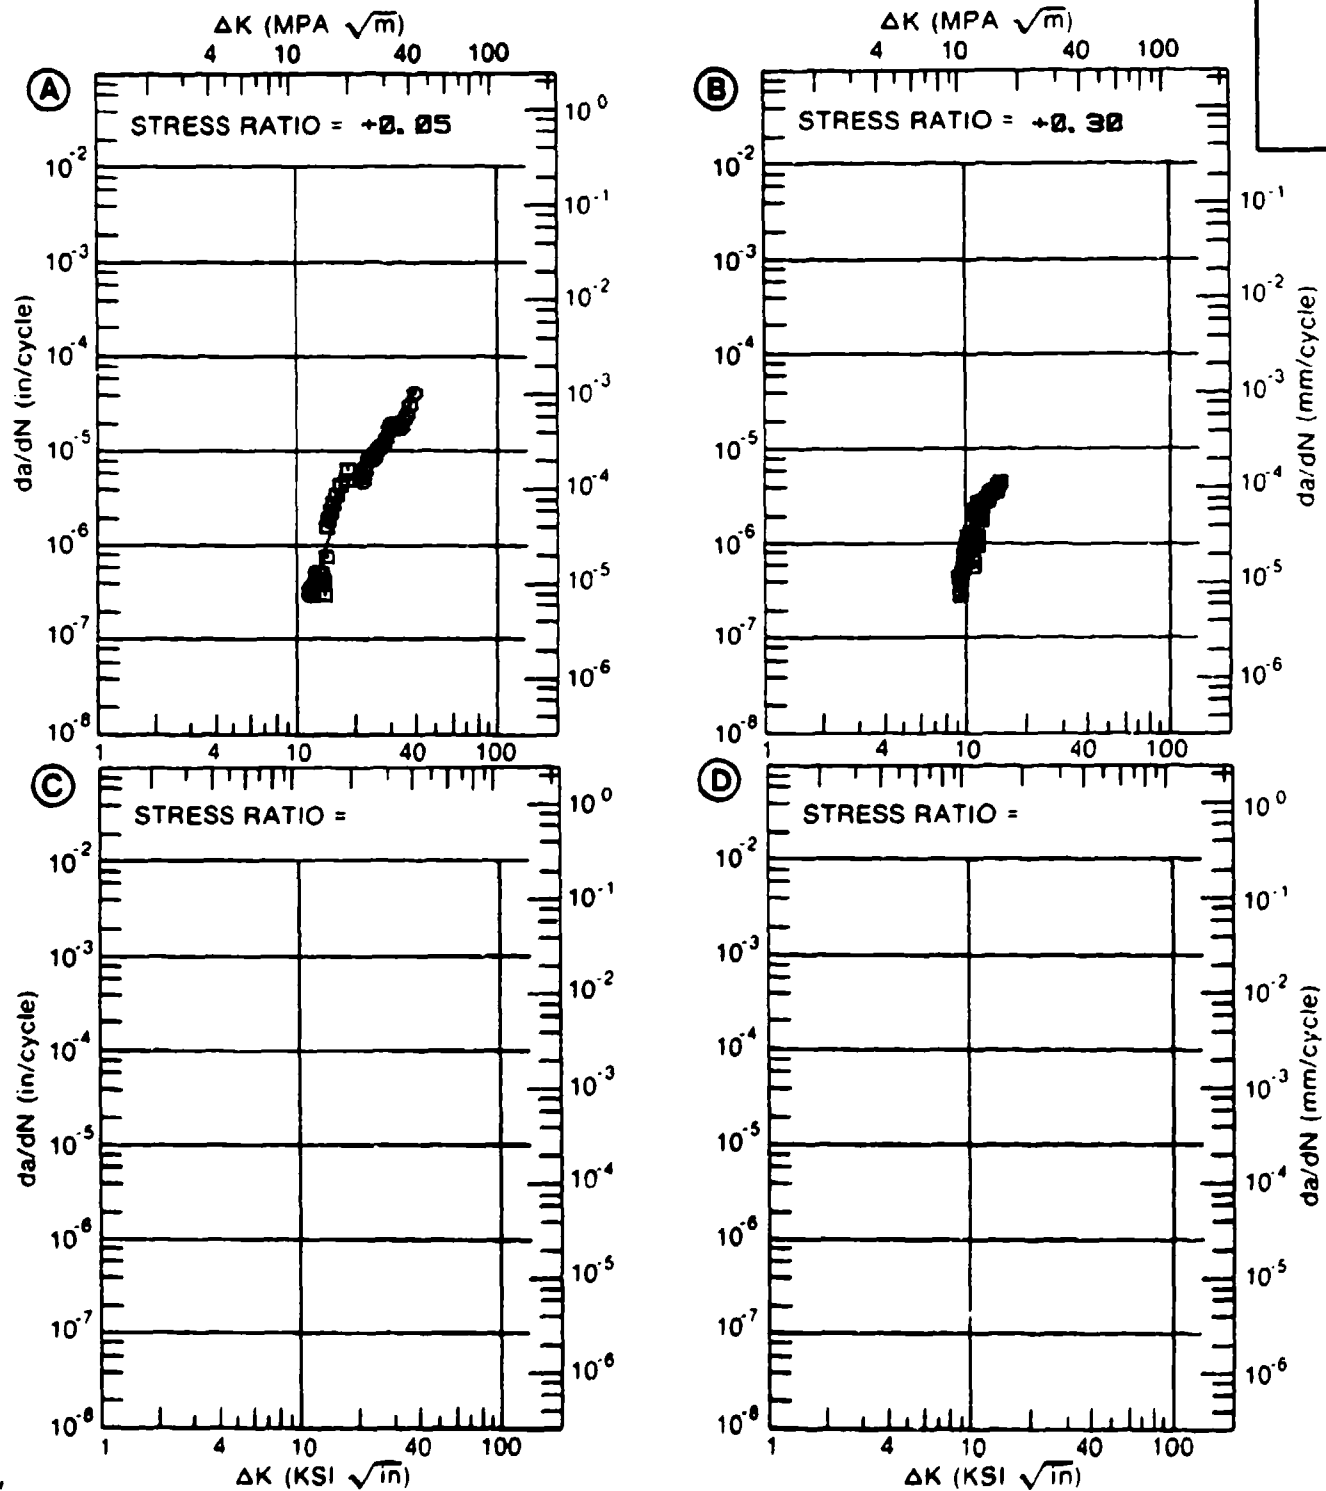


Figure 4.11.3.49

TABLE 4.11.3.50

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.50 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		LAB AIR			
DELTA K	A: 31.29	17.0			
MIN	B:				
	C:				
	D:				
	35.00	25.5			
	40.00	39.6			
	50.00	96.5			
DELTA K	A: 59.30	220.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE	8.28				
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.04
 FREQUENCY: 20.00 HZ

YIELD STRENGTH: 135.3 KSI
 ULT. STRENGTH: 137.6 KSI
 SPECIMEN THK: 0.290"
 SPECIMEN WIDTH: 6.011"
 REFERENCES: 98468

TITAN.
 ALLOY

TI-6AL-
 4V

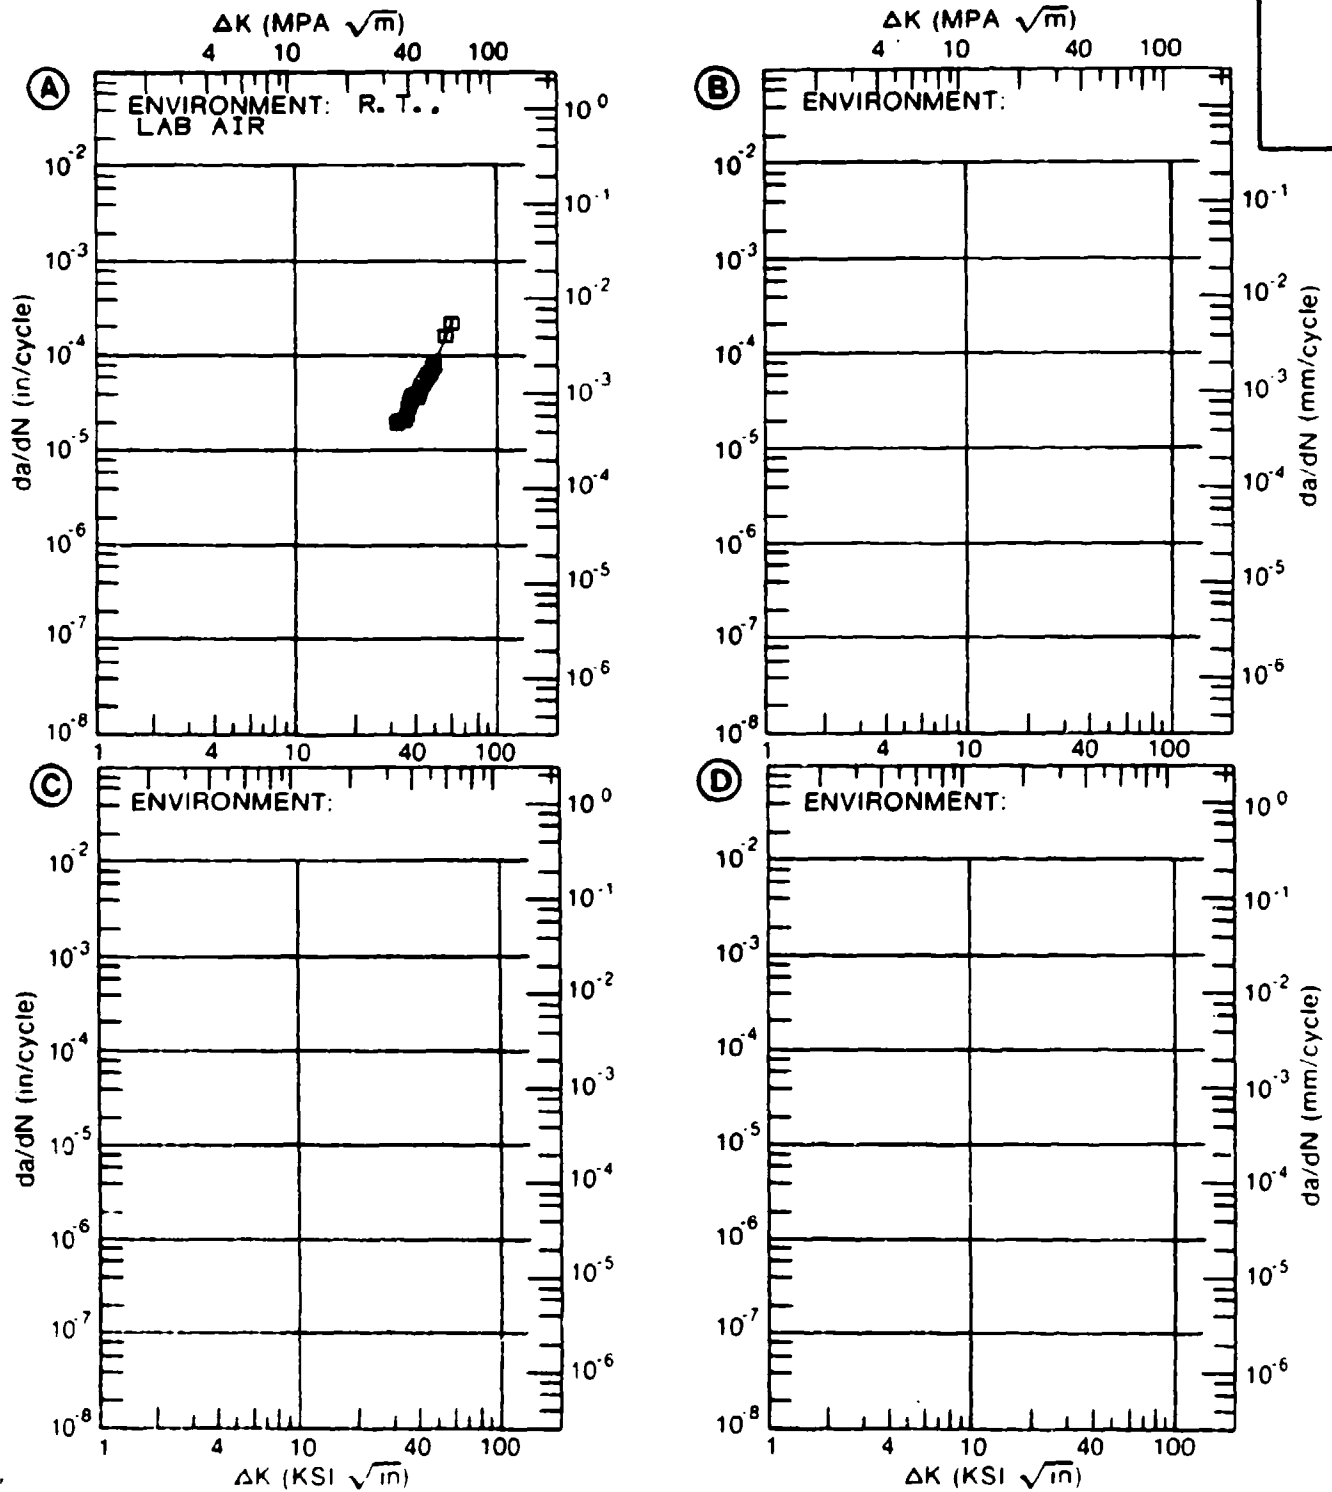


Figure 4.11.3.50

TABLE 4.11.3.51

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.51 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: MA
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=-1.00	R=+0.50		
DELTA K	A: 8.85	.632			
MIN	B: 5.43		.380		
	C:				
	D:				
	6.00		.734		
	7.00		1.77		
	8.00		3.40		
	9.00	.688	5.65		
	10.00	1.14	8.52		
	13.00	3.27	21.2		
	16.00	6.55	41.9		
	20.00	12.8	92.4		
	25.00	24.8	206.		
	30.00	44.0	316.		
	35.00	75.3	381.		
	40.00	127.	524.		
	50.00	328.			
	60.00	724.			
	70.00	1345.			
	80.00	2115.			
	90.00	2858.			
DELTA K	A: 92.48	3016.			
MAX	B: 49.27		1688.		
	C:				
	D:				

ROOT MEAN SQUARE 10.15 18.86
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: MA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 132.5 KSI
 ULT. STRENGTH: 138.0 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: MA006

TITAN.
 ALLOY

TI-6AL-
 4V

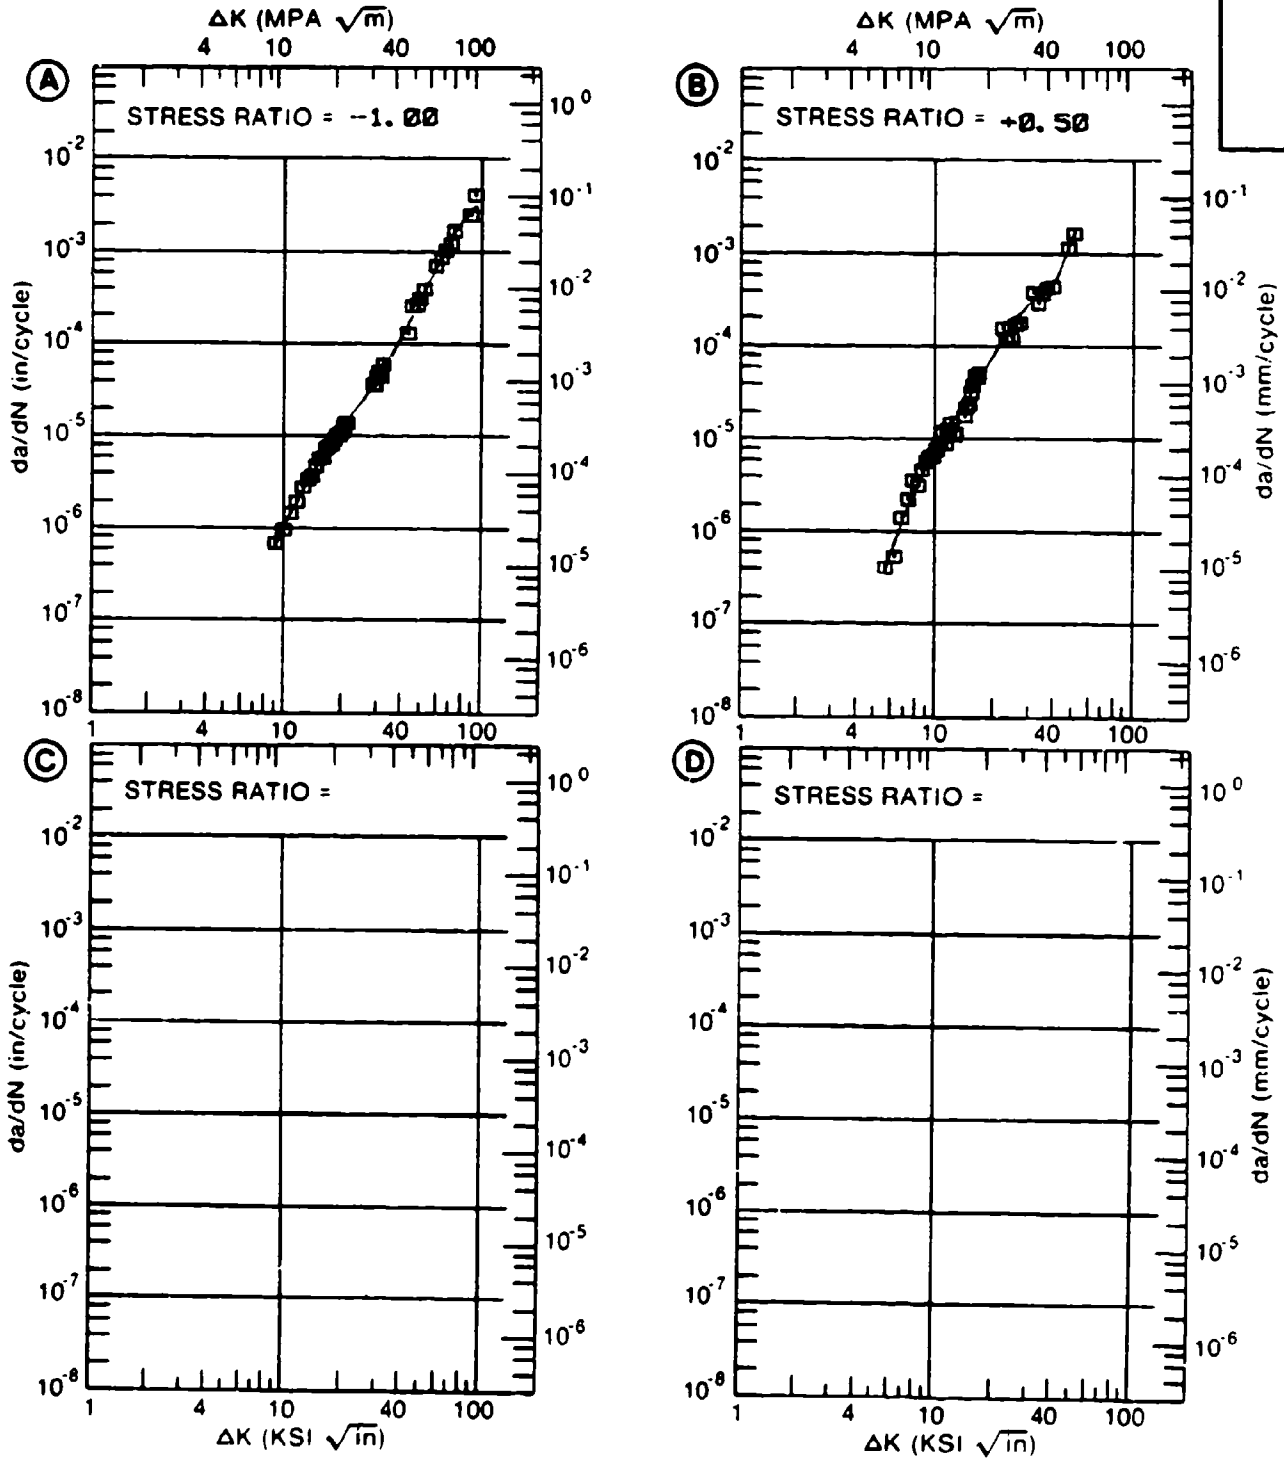


Figure 4.11.3.51

TABLE 4.11.3.52

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.52 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E=- 65F	E=+ 175F		
		AIR	AIR		
DELTA K	A: 25.62	26.3			
MIN	B: 17.93		8.57		
	C:				
	D:				
	20.00		11.7		
	25.00		20.6		
	30.00	55.6	31.8		
	35.00	158.	46.5		
	40.00	1500.	66.6		
	50.00		135.		
	60.00		280.		
DELTA K	A: 41.96	5475.			
MAX	B: 65.73		429.		
	C:				
	D:				
ROOT MEAN SQUARE		39.40	11.28		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 0.10- 10.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: 00144

TITAN.
 ALLOY

TI-6AL-
 4V

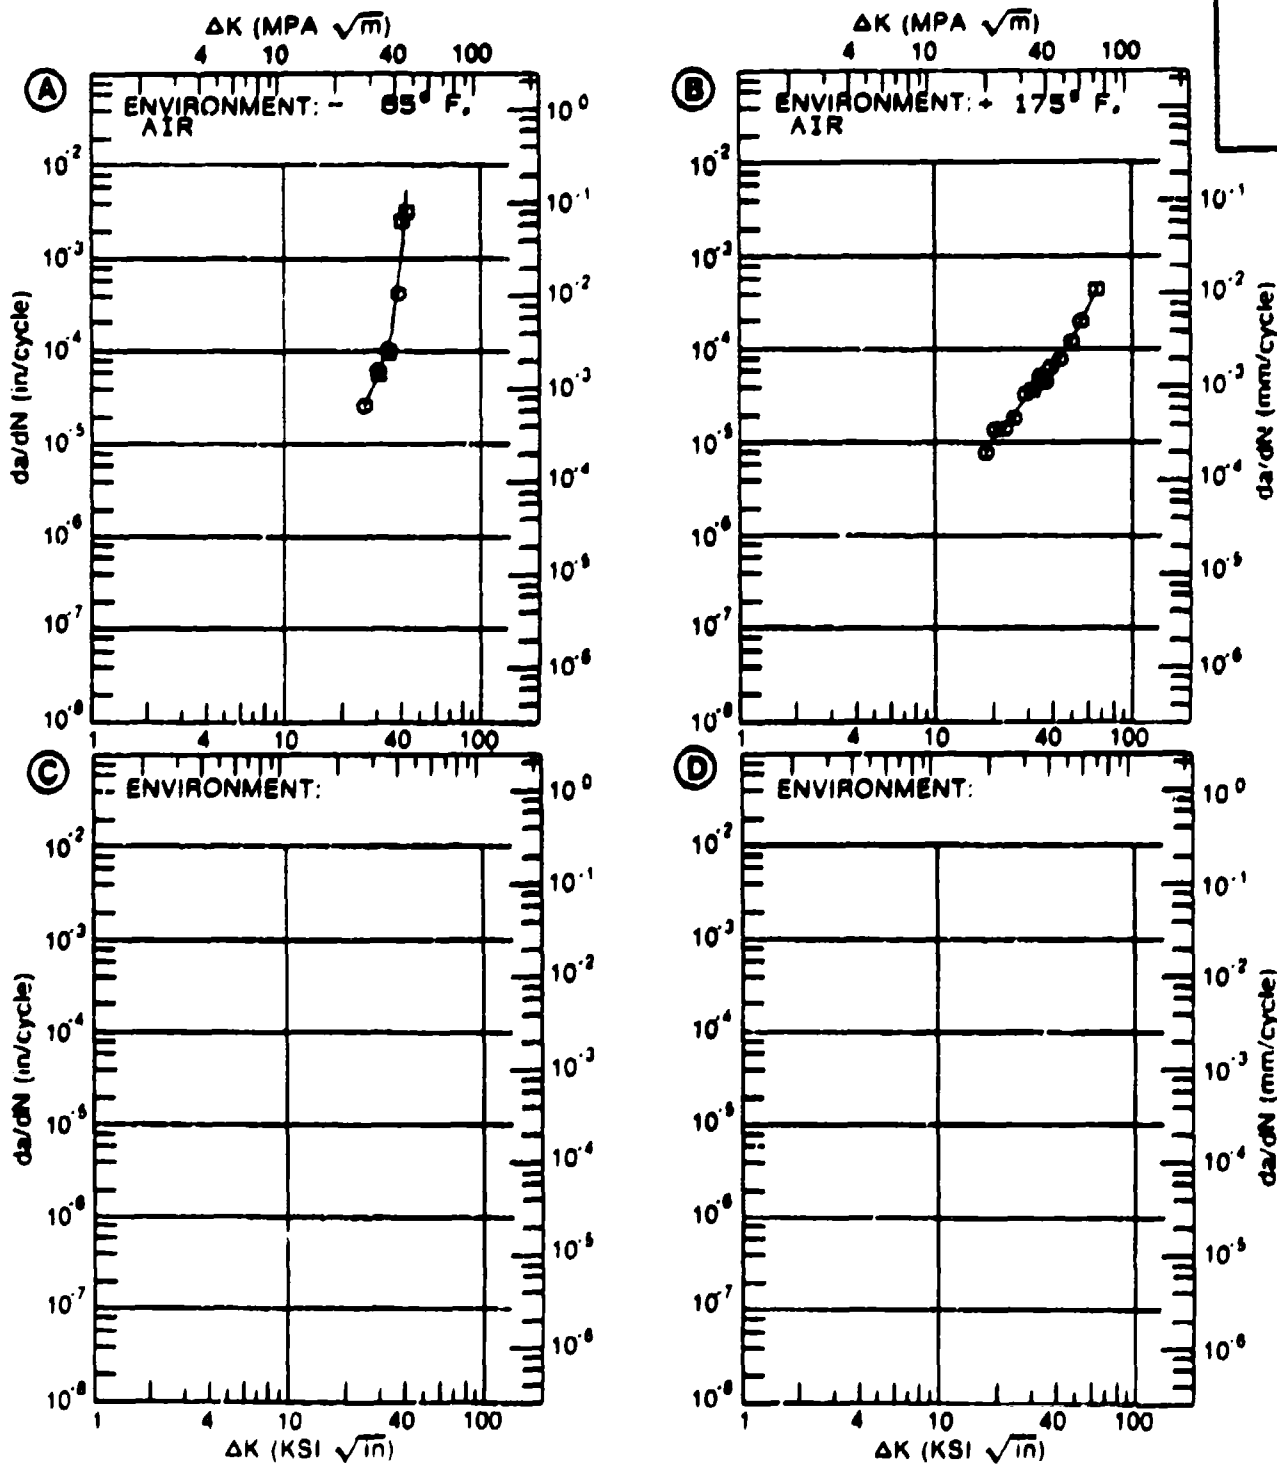


Figure 4.11.3.52

TABLE 4.11.3.53

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.53 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. L. H. A. 1-6HZ	E= R. T. S. T. W. 1HZ		
DELTA K	A: 6.95	.123			
MIN	B: 8.19		.441		
	C:				
	D:				
	7.00	.127			
	8.00	.203			
	9.00	.286	.436		
	10.00	.415	.589		
	13.00	2.22	2.89		
	16.00	9.87	11.3		
	20.00	24.7	31.5		
	25.00	38.2	58.6		
	30.00	49.7	77.8		
	35.00	68.7			
	40.00	109.			
	50.00	402.			
DELTA K	A: 55.67	771.			
MAX	B: 32.78		84.7		
	C:				
	D:				
ROOT MEAN SQUARE		14.83	22.37		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8		1		
RATIO	0.8-1.25	2	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: 1.25" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.30
 FREQUENCY:

YIELD STRENGTH: 120.0 KSI
 ULT. STRENGTH: 134.0 KSI
 SPECIMEN THK: 0.990- 0.997"
 SPECIMEN WIDTH: 6.000- 6.010"
 REFERENCES: 05837

TITAN.
 ALLOY

TI-6AL-
 4V

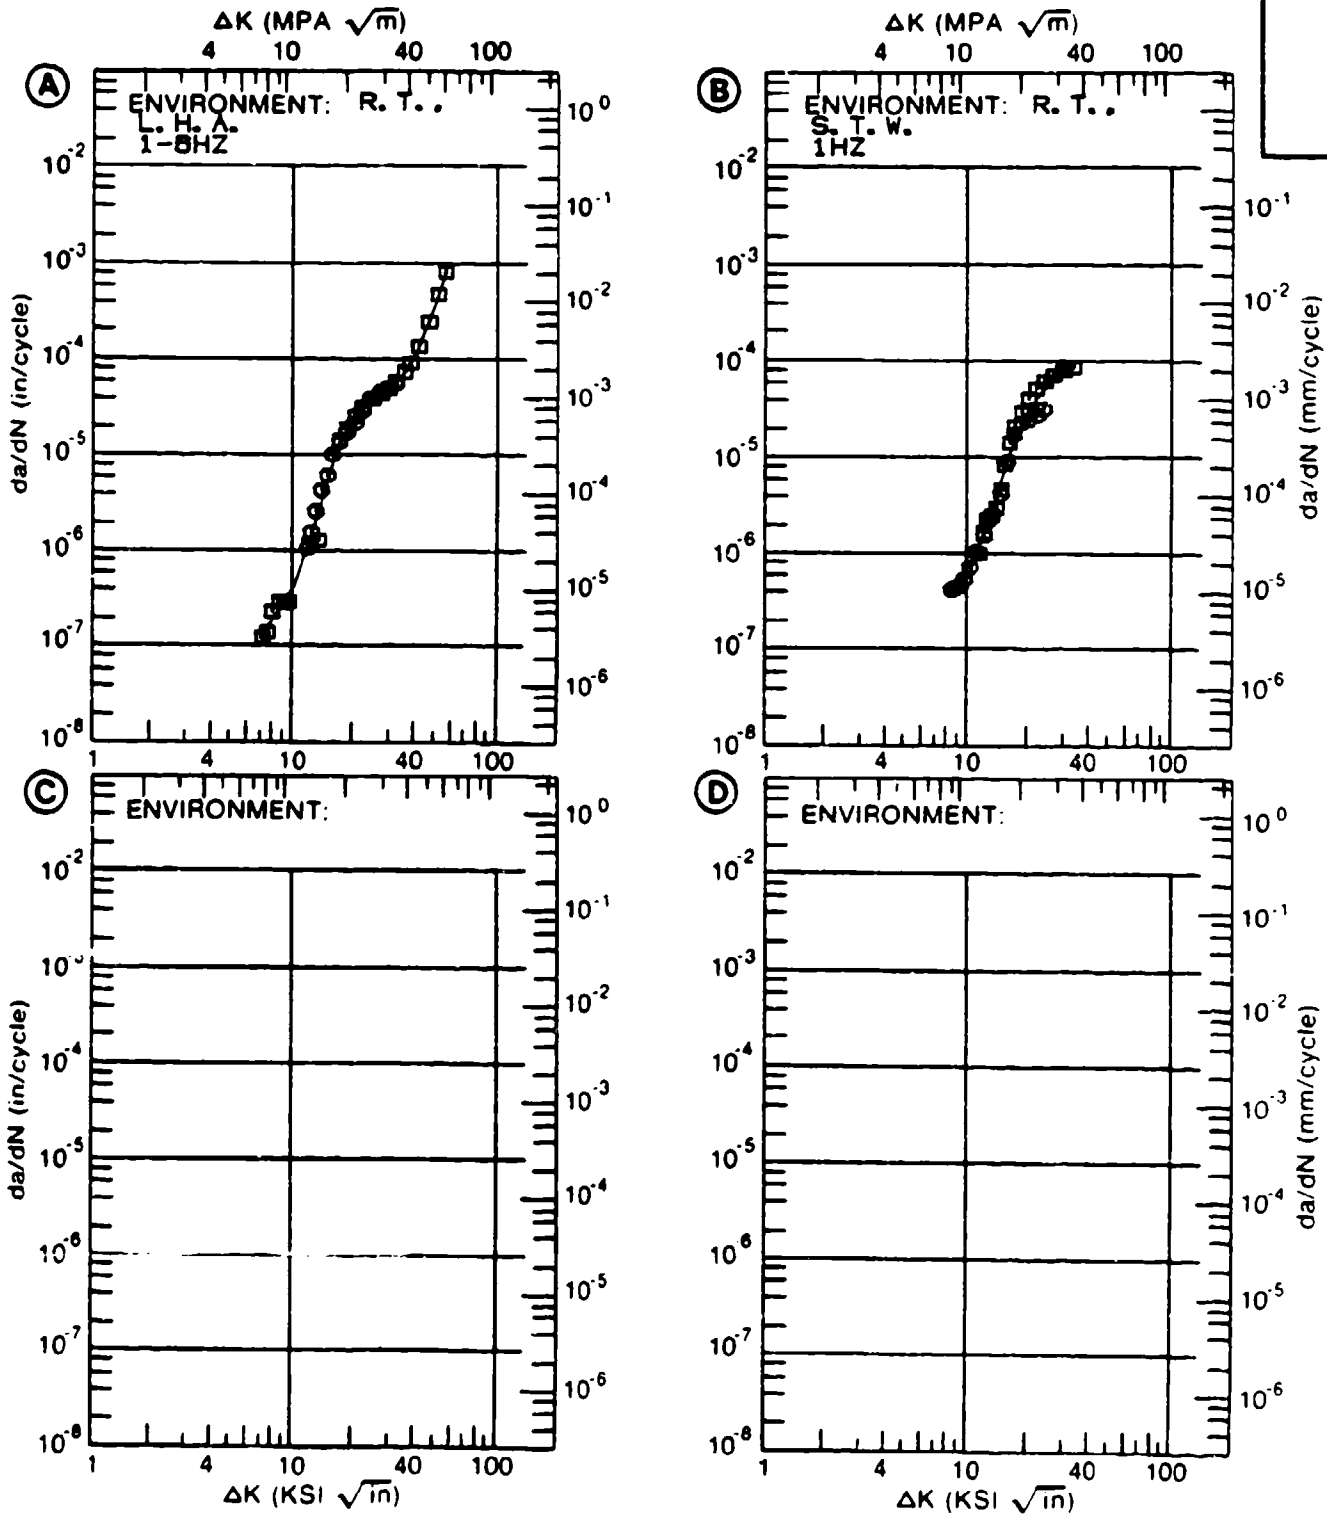


Figure 4.11.3.53

TABLE 4.11.3.54

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.54 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: MA
ENVIRONMENT: R. T. , L. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.30			
A:	6.36	.14			
DELTA K B:					
MIN C:					
D:					
	7.00	.147			
	8.00	.195			
	9.00	.293			
	10.00	.460			
	13.00	1.63			
	16.00	4.30			
	20.00	11.2			
	25.00	26.4			
	30.00	48.3			
	35.00	75.9			
	40.00	113.			
	50.00	255.			
A:	58.57	557.			
DELTA K B:					
MAX C:					
D:					

ROOT MEAN SQUARE 12.47
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: MA
 FORM: 1.5" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00- 6.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 120.1 KSI
 ULT. STRENGTH: 134.1 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 8.000"
 REFERENCES: 94301

TITAN.
 ALLOY

TI-6AL-
 4V

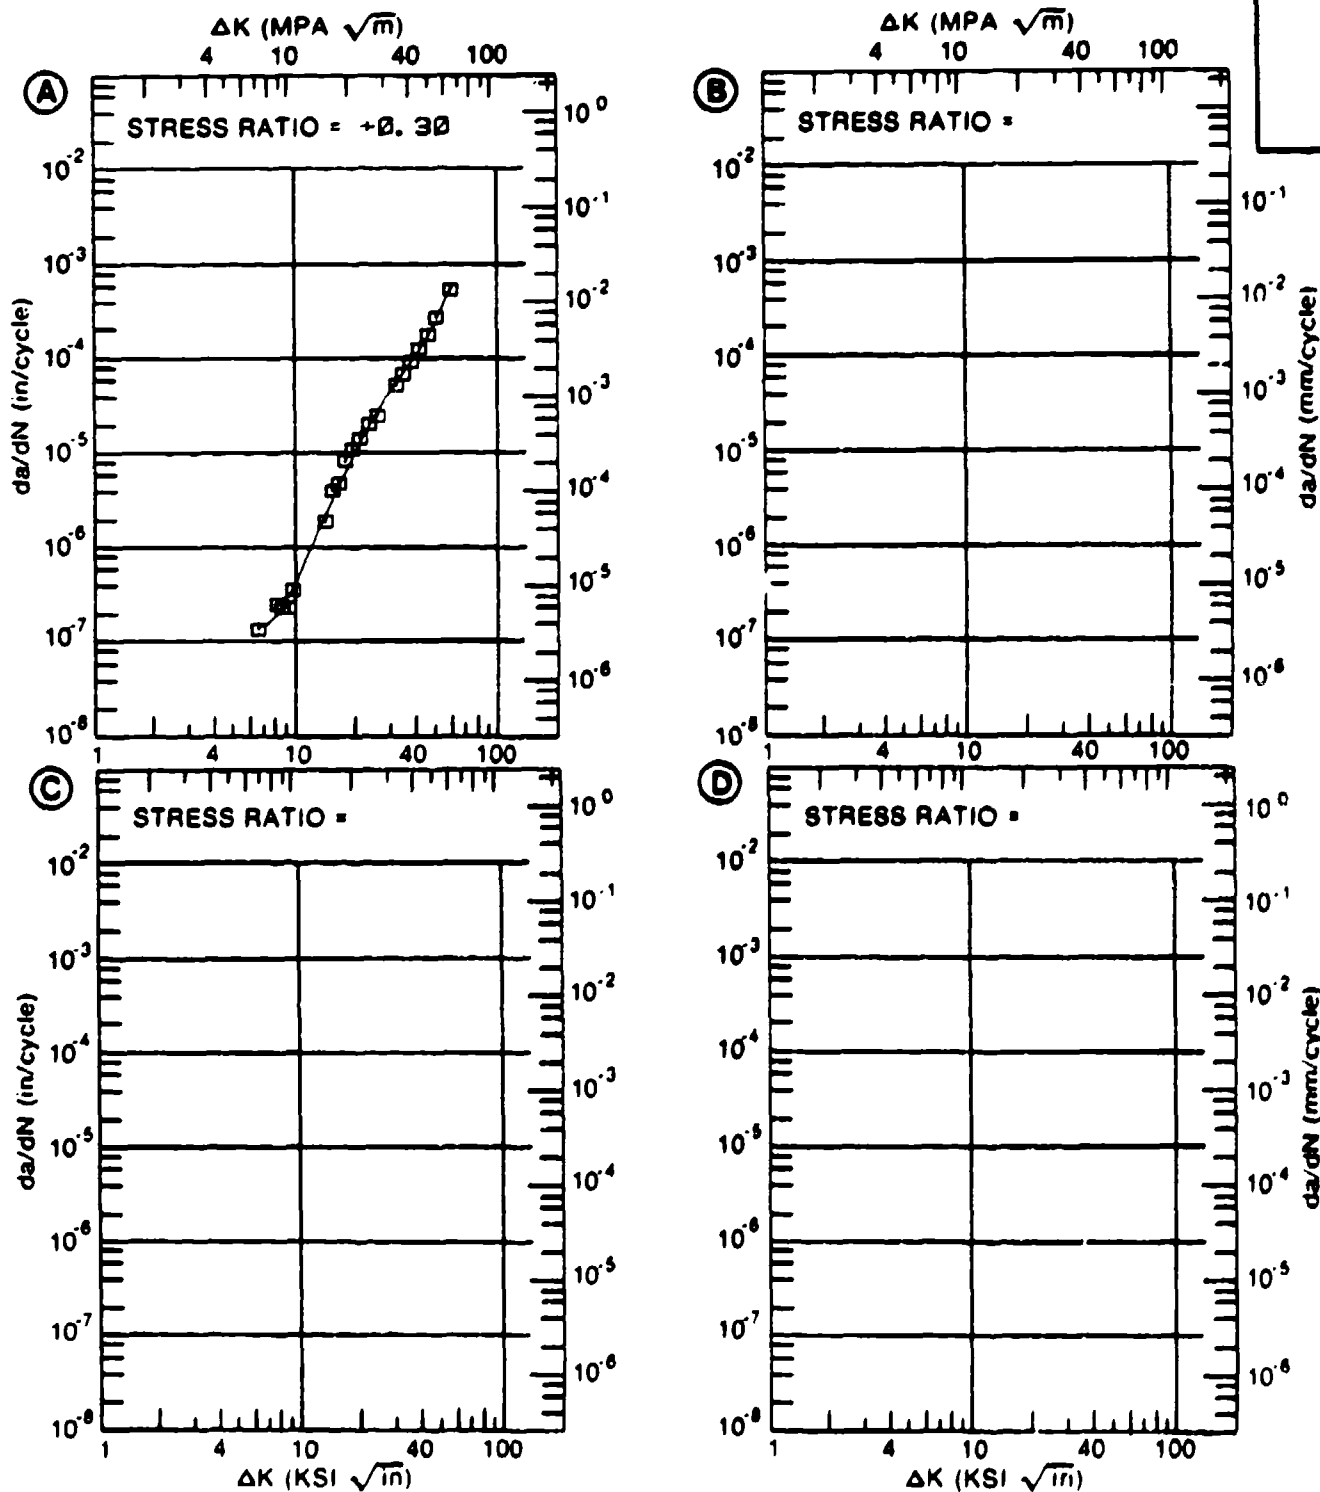


Figure 4.11.3.54

TABLE 4.11.3.55

**FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR**

DATA ASSOCIATED WITH FIGURE 4.11.3.55 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.02			
DELTA K	A: 5.91	.0335			
MIN	B:				
	C:				
	D:				
	6.00	.0340			
	7.00	.0448			
	8.00	.0653			
	9.00	.0996			
	10.00	.154			
	13.00	.554			
	16.00	1.71			
	20.00	5.92			
	25.00	19.4			
	30.00	46.1			
	35.00	86.0			
	40.00	133.			
DELTA K	A: 44.29	171.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		35.86			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 0.10- 30.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 133.0 KSI
 ULT. STRENGTH: 142.0 KSI
 SPECIMEN THK: 0.188- 0.191"
 SPECIMEN WIDTH: 3.957- 3.964"
 REFERENCES: MA002

TITAN.
 ALLOY

TI-6AL-
 4V

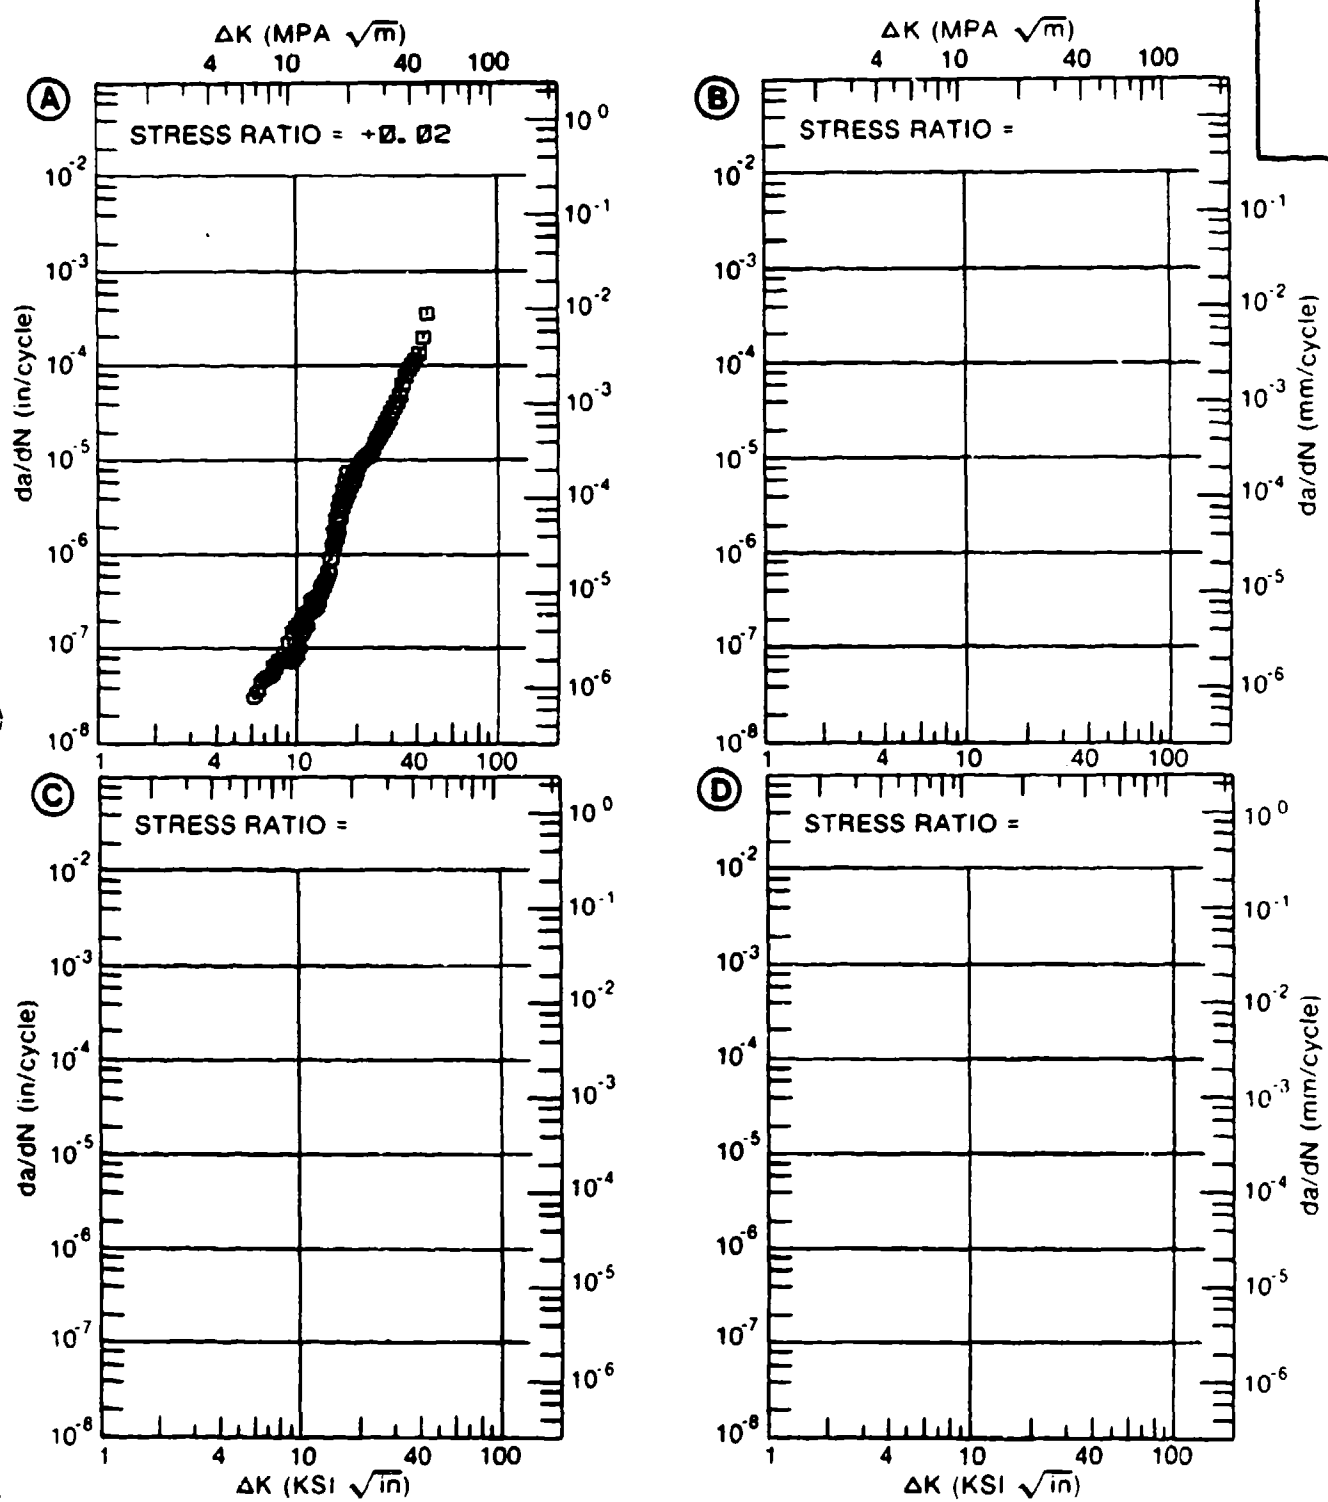


Figure 4.11.3.55

TABLE 4.11.3.56

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.56 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
ENVIRONMENT: R. T. , L. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30	R=+0.50	
DELTA K	A: 7.76	.147			
MIN	B: 11.48		1.20		
	C: 10.32			1.70	
	D:				
	8.00	.161			
	9.00	.241			
	10.00	.373			
	13.00	1.36	3.31	5.53	
	16.00	4.04	9.32	9.75	
	20.00	11.7	16.8	17.3	
	25.00	25.9	38.1	47.0	
	30.00	36.2	66.0	94.0	
DELTA K	A: 34.01	36.7			
MAX	B: 30.00		66.0		
	C: 30.83			94.6	
	D:				
ROOT MEAN SQUARE		21.28	14.01	8.00	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2	1	1	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 8.88 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 122.0- 123.5 KSI
 ULT. STRENGTH: 135.5- 139.0 KSI
 SPECIMEN THK: 0.003- 0.007"
 SPECIMEN WIDTH: 3.770- 4.948"
 REFERENCES 95837

TITAN.
 ALLOY

TI-6AL-
 4V

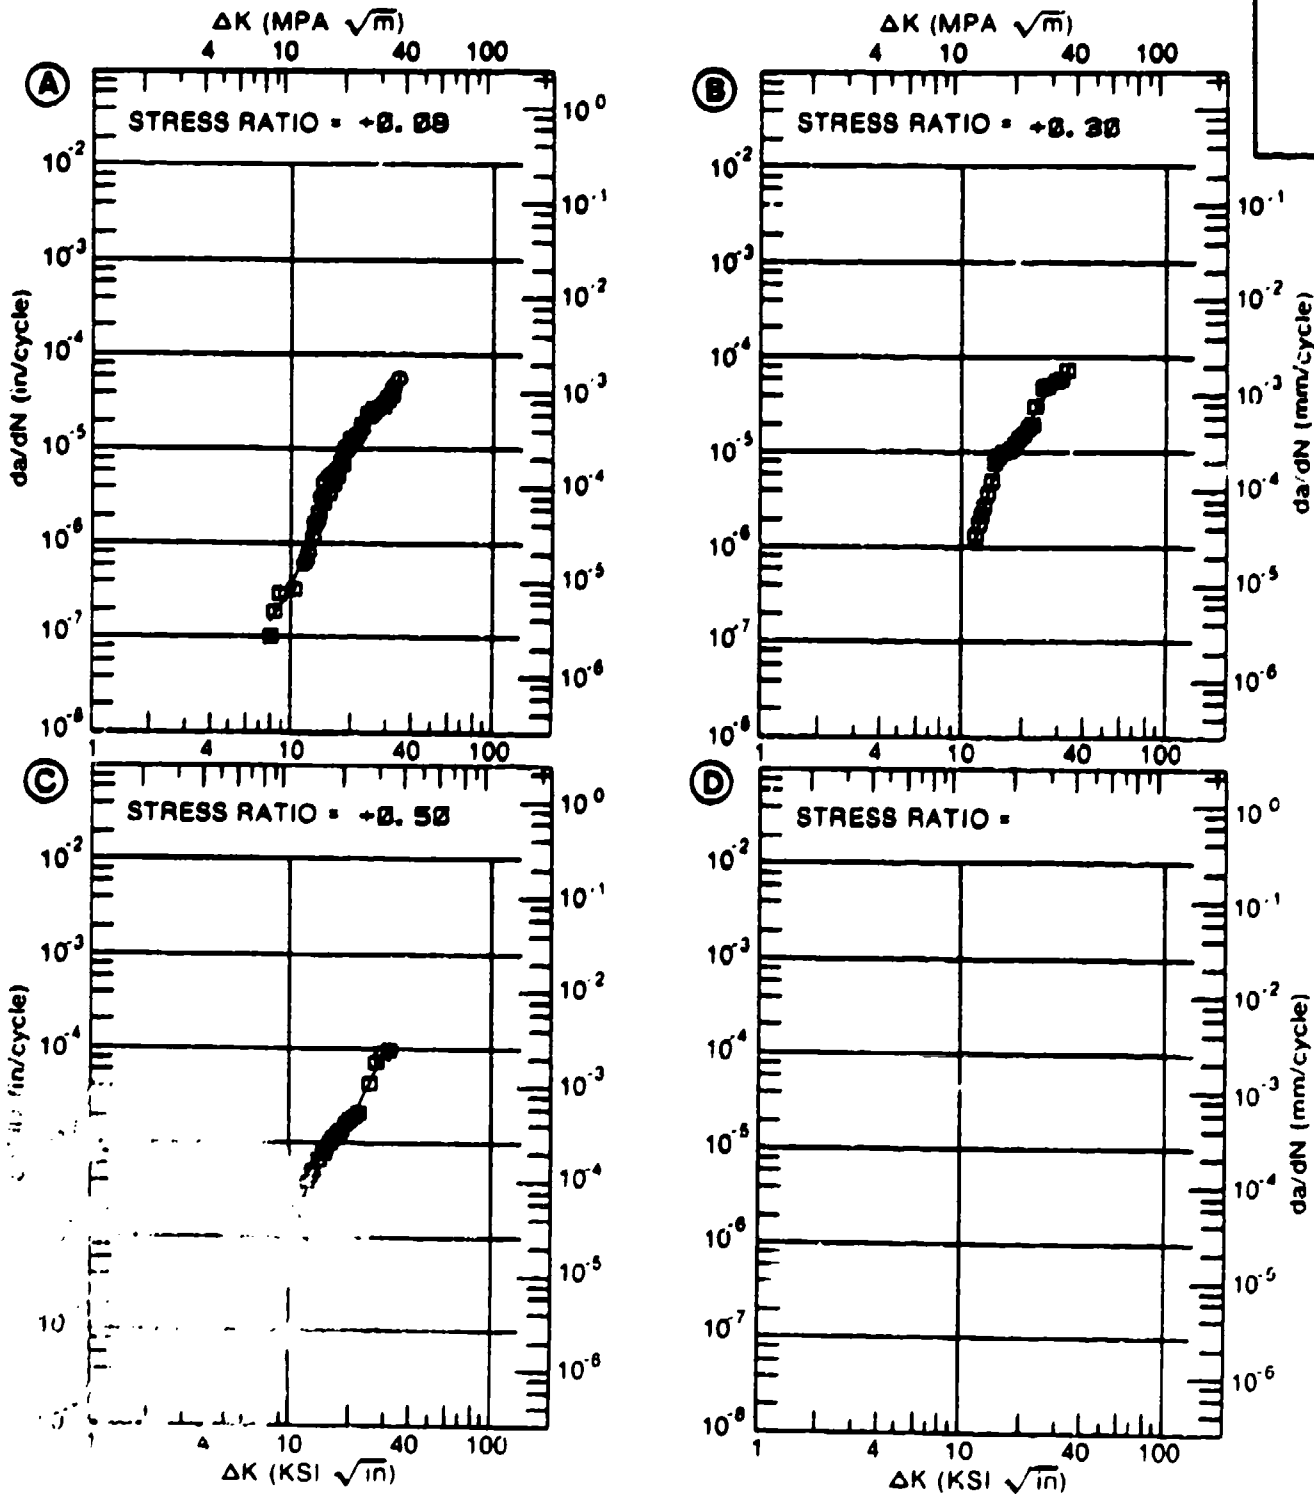


Figure 4.11.3.56

TABLE 4.11.3.57

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.57 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. J. P. 4	E= R. T. S. T. W.	
DELTA K	A: 13.17	1.51			
MIN	B: 18.10		8.27		
	C: 11.48			1.35	
	D:				
	13.00			1.82	
	16.00	5.07		5.04	
	20.00	13.9	12.0	14.3	
	25.00	28.7	25.1	32.4	
	30.00	46.5	43.5	53.9	
	35.00	68.2	68.4	80.4	
	40.00	97.1	103.	117.	
	50.00			266.	
DELTA K	A: 42.59	116.			
MAX	B: 46.81		171.		
	C: 51.63			308.	
	D:				
ROOT MEAN SQUARE		13.77	3.38	8.04	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1	1	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 123.5- 127.0 KSI
 ULT. STRENGTH: 135.5- 139.0 KSI
 SPECIMEN THK: 0.994- 1.000"
 SPECIMEN WIDTH: 3.770"
 REFERENCES: 85837, 88579

TITAN.
 ALLOY

TI-6AL-
 4V

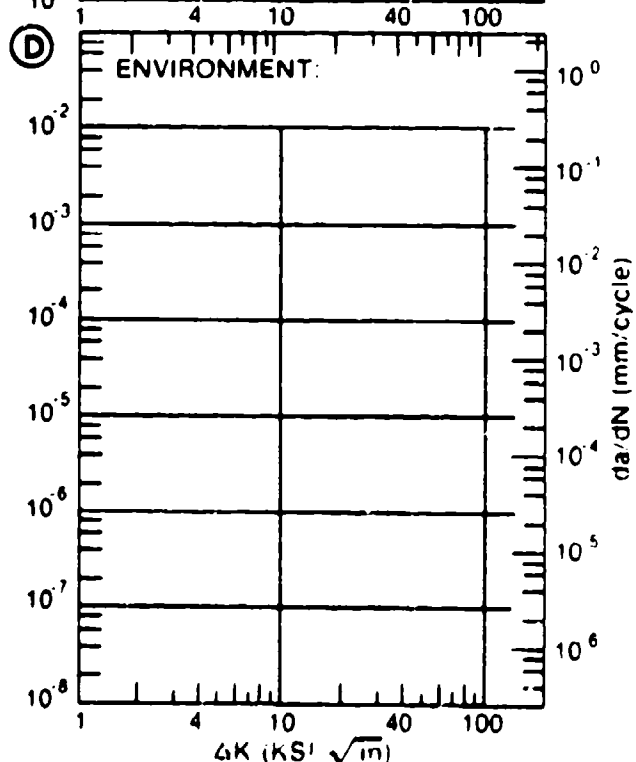
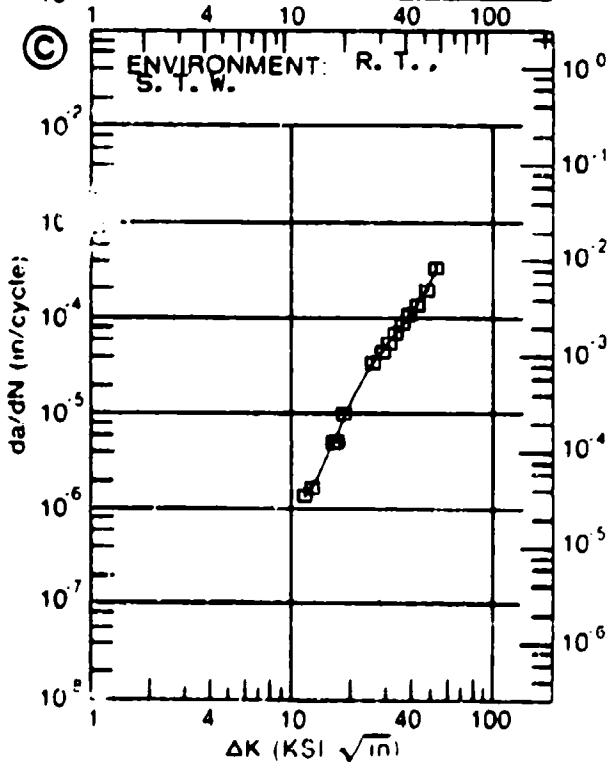
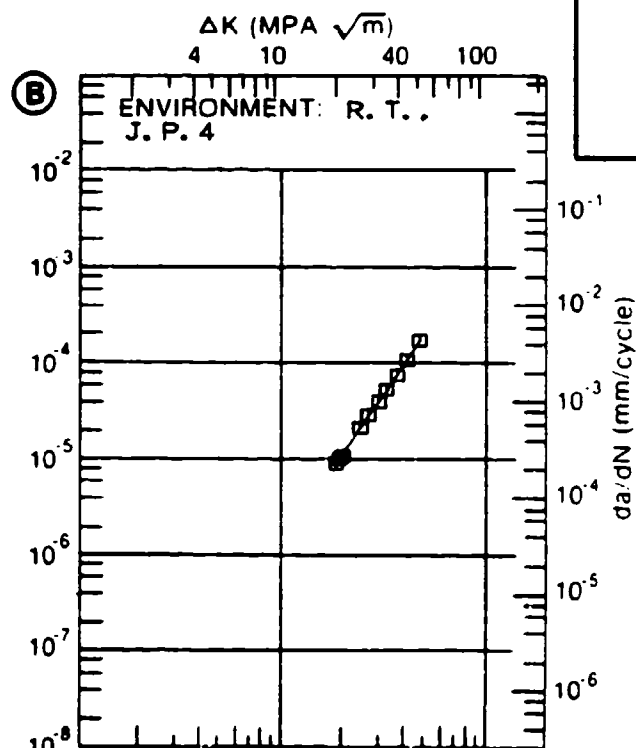
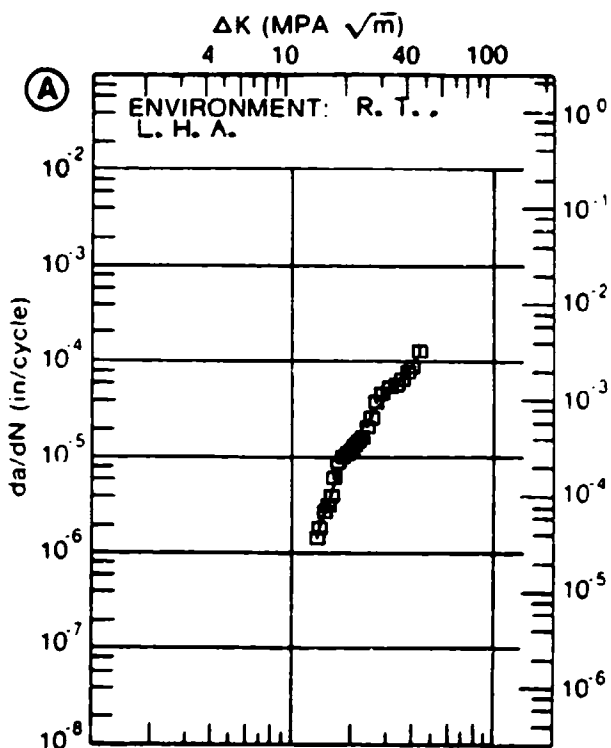


Figure 4.11.3.57

TABLE 4.11.3.58

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.58 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A. 6HZ	E= R. T. S. T. W. 6HZ		
DELTA K	A: 13.81	1.76			
MIN	B: 9.22		.428		
	C:				
	D:				
	10.00		.620		
	13.00		1.97		
	16.00	5.21	4.67		
	20.00	12.7	11.1		
	25.00	15.9	24.8		
	30.00	36.0	45.1		
	35.00		71.6		
DELTA K	A: 32.77	90.6			
MAX	B: 39.27		98.5		
	C:				
	D:				
ROOT MEAN SQUARE		16.43	6.59		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 125.0 KSI
 ULT. STRENGTH: 142.0 KSI
 SPECIMEN THK: 0.994"
 SPECIMEN WIDTH: 3.770"
 REFERENCES: 05837

TITAN.
 ALLOY

TI-6AL-
 4V

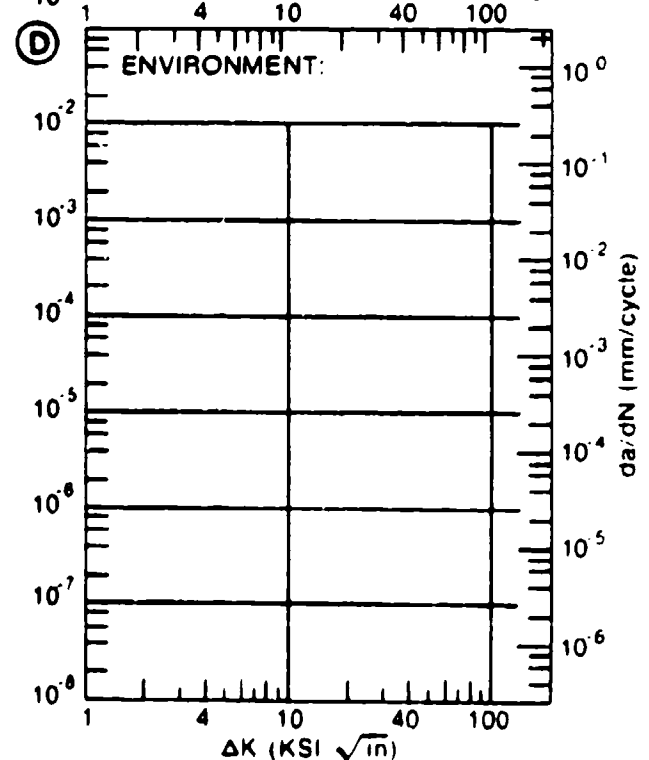
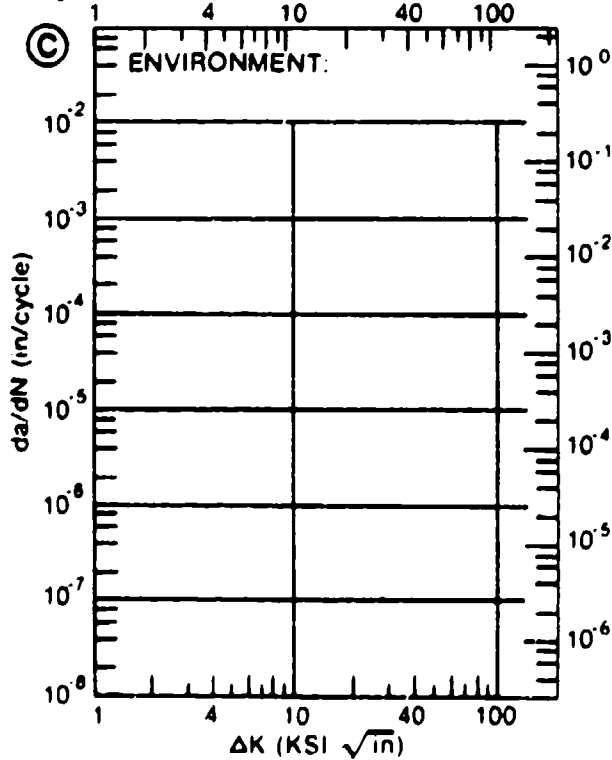
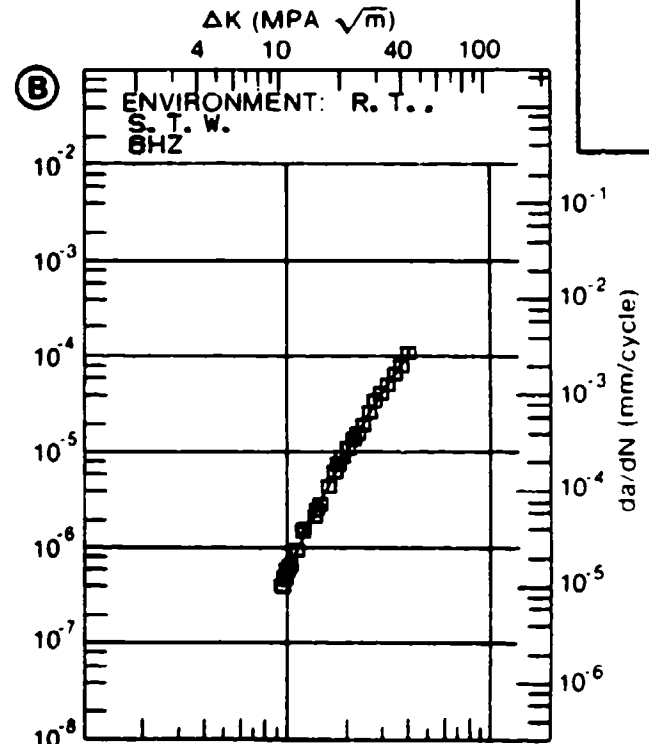
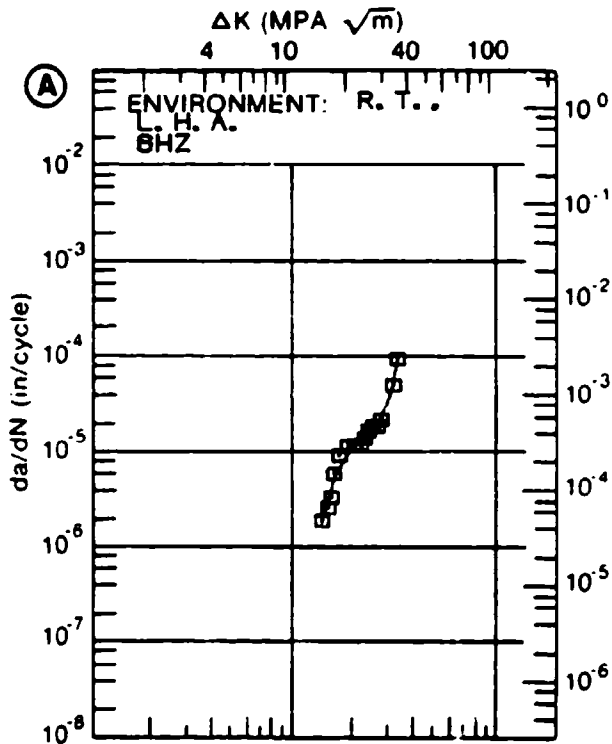


Figure 4.11.3.58

TABLE 4.11.3.59

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.59 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR 1-20HZ	E= R. T. S. T. W. 1-10HZ	E= R. T. SIM. SEA WATER 1-10HZ	
DELTA K A:	12.95	.690			
DELTA K B:	10.86		1.21		
MIN C:	10.22			.987	
D:					
	13.00	.712	2.42	2.42	
	16.00	3.12	5.16	4.84	
	20.00	9.50	11.2	9.69	
	25.00	21.0	23.9	19.3	
	30.00	35.6	43.9	34.5	
	35.00	55.1	73.8	58.5	
	40.00	83.7	116.	95.9	
	50.00	202.	254.	242.	
	60.00	548.	496.	580.	
	70.00	1660.			
DELTA K A:	74.97	2988.			
DELTA K B:	60.69		518.		
MAX C:	66.66			1019.	
D:					
ROOT MEAN SQUARE		18.14	27.52	31.04	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2	2	2	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: 1.00" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY:

YIELD STRENGTH: 124.4 KSI
 ULT. STRENGTH: 135.3 KSI
 SPECIMEN THK: 1.000- 1.003"
 SPECIMEN WIDTH: 4.500"
 REFERENCES: NC002

TITAN.
 ALLOY

TI-6AL-
 4V

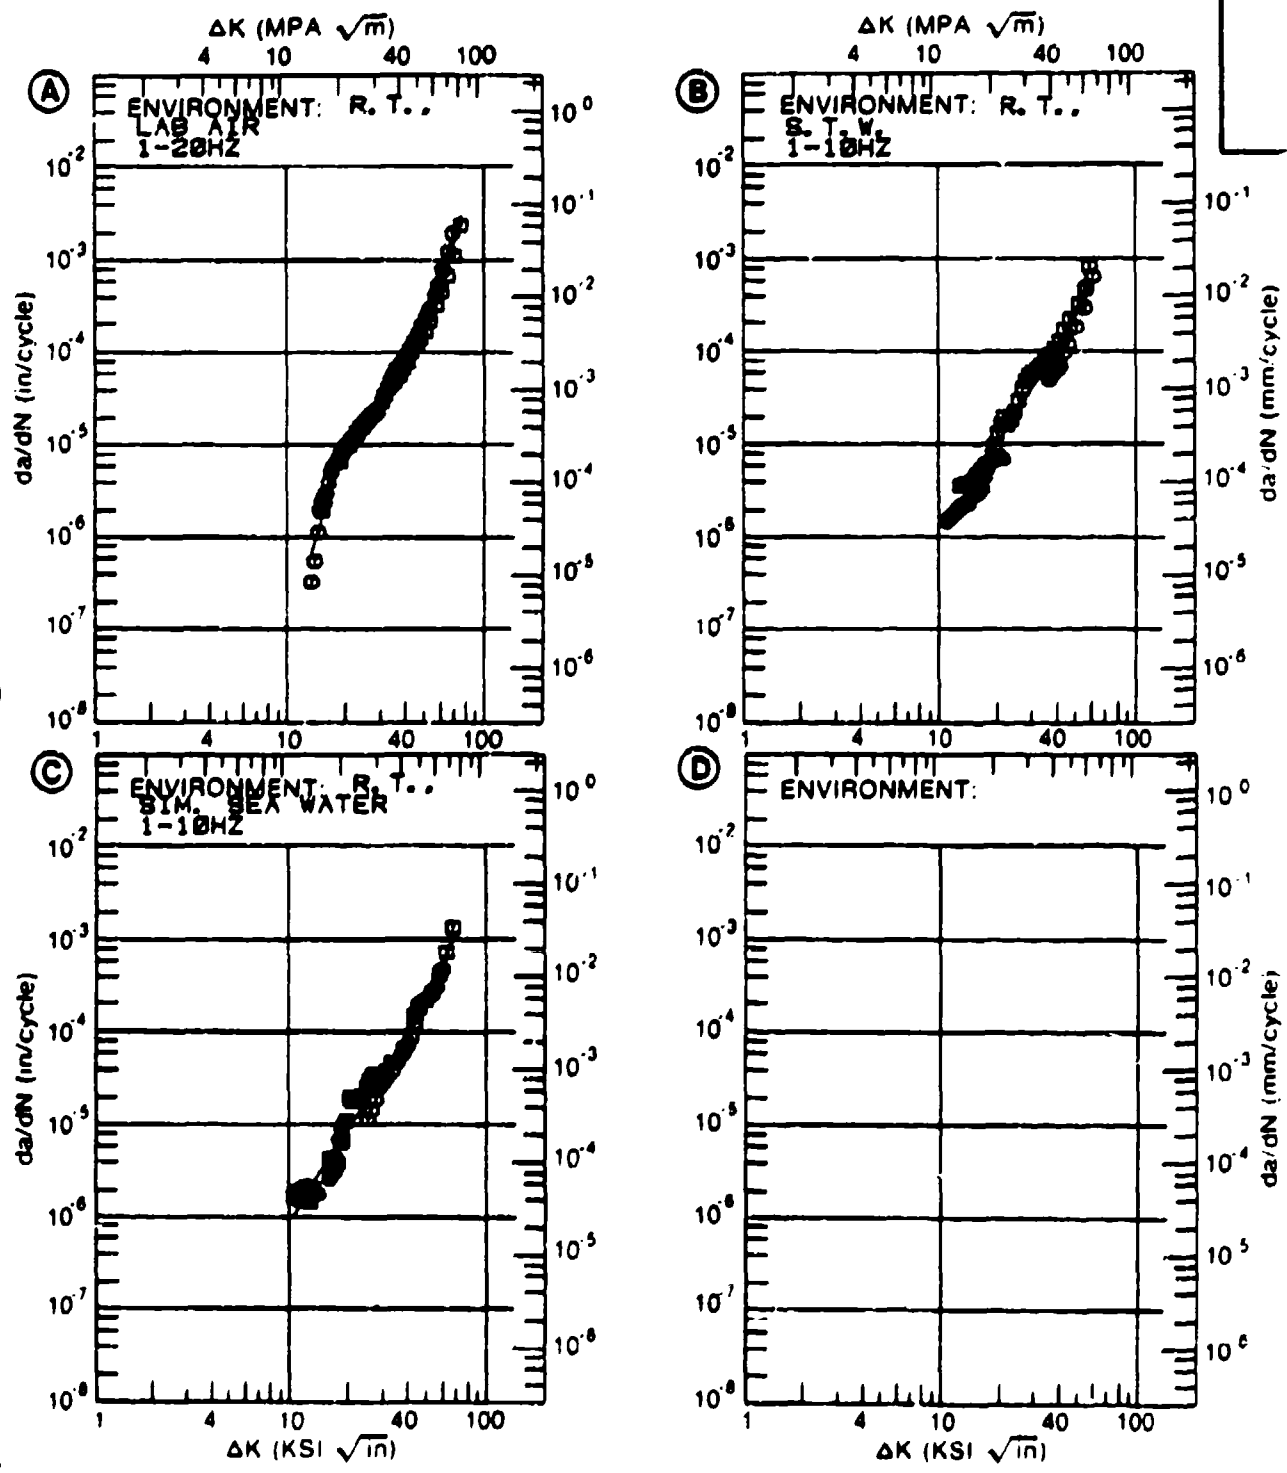


Figure 4.11.3.50

TABLE 4.11.3.60

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.60 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR 5-20HZ	E= R. T. S. T. W. 1-10HZ	E= R. T. SIM. SEA WATER 1-10HZ	
DELTA K	A: 11.73	1.23			
MIN	B: 10.98		2.31		
	C: 10.52			2.98	
	D:				
	13.00	2.34	4.93	3.88	
	16.00	6.39	11.3	9.08	
	20.00	13.7	25.9	18.0	
	25.00	24.8	47.7	31.2	
	30.00	39.5	67.3	47.3	
	35.00	61.7	90.6	69.1	
	40.00	98.6	128.	100.	
	50.00	281.	324.	220.	
	60.00			538.	
DELTA K	A: 59.40	863.			
MAX	B: 56.74		737.		
	C: 63.55			874.	
	D:				
ROOT MEAN SQUARE		11.97	17.66	28.94	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8			1	
RATIO	0.8-1.25	2	2		
SUMMARY	1.25-2.0			1	
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: 1.00" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY:

YIELD STRENGTH: 126.6 KSI
 ULT. STRENGTH: 138.6 KSI
 SPECIMEN THK: 1.000-1.003"
 SPECIMEN WIDTH: 4.500"
 REFERENCES: NC002

TITAN.
 ALLOY

TI-6AL-
 4V

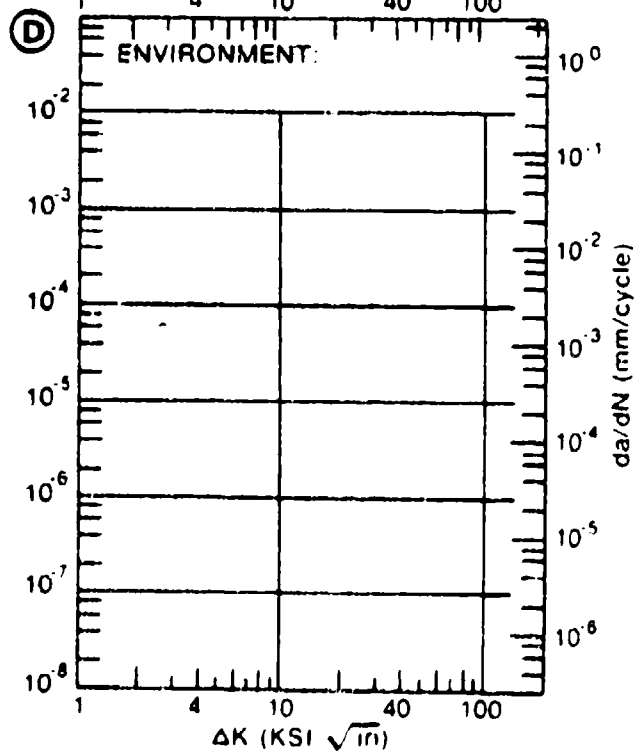
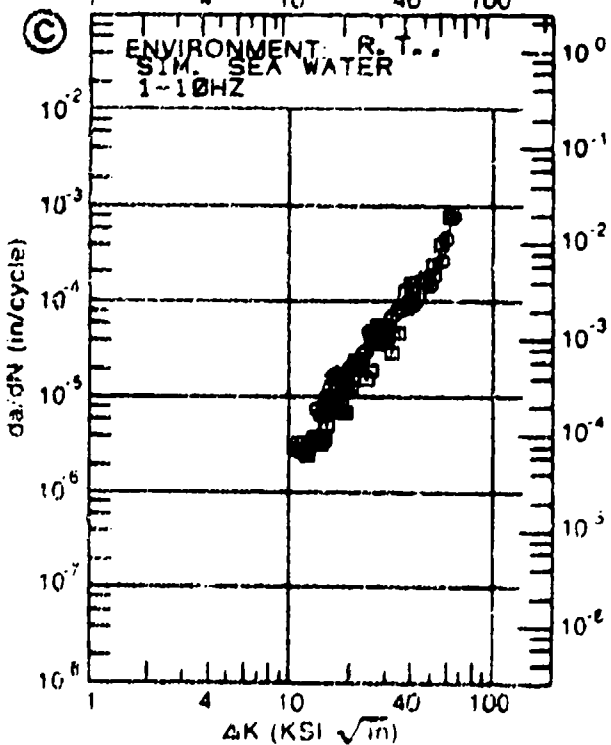
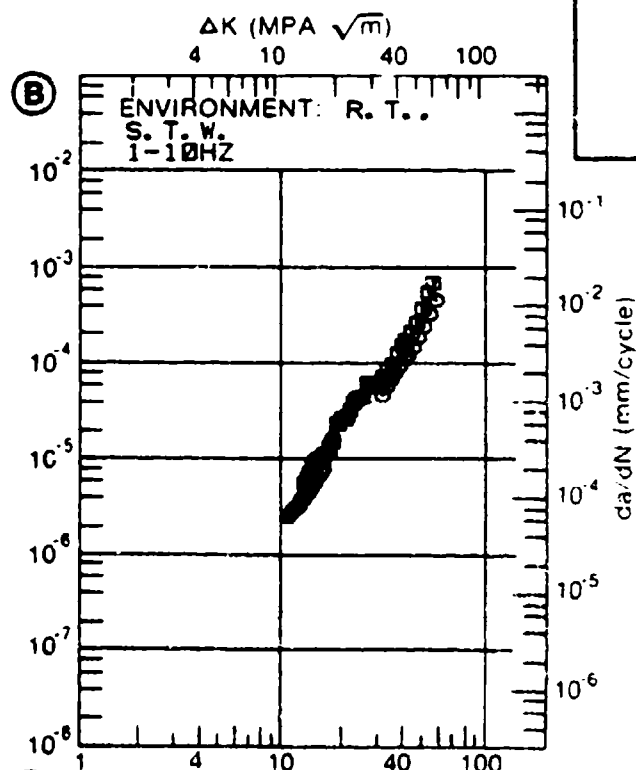
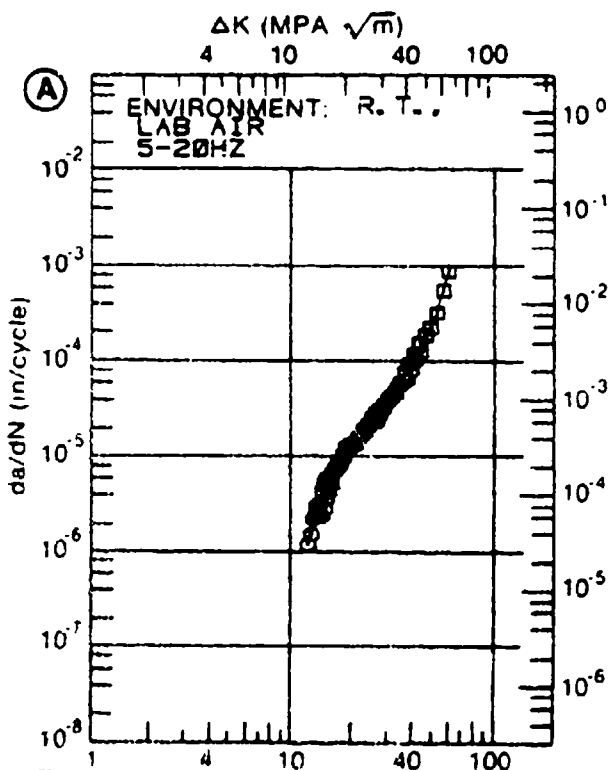


Figure 4.11.3.69

TABLE 4.11.3.61

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.61 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY ARGON 10HZ	E= R. T. DRY AIR 08-10HZ	E= R. T. SIMULATED FUEL 09-10HZ	
DELTA K	A:				
MIN	B:	15.25	5.87		
	C:	13.51		2.61	
	D:				
	16.00		7.15	5.95	
	20.00		15.6	14.2	
	25.00		30.9	31.1	
	30.00		55.5	63.1	
	35.00		99.4	130.	
	40.00		183.	280.	
	50.00		696.	1513.	
DELTA K	A:				
MAX	B:	51.67	882.		
	C:	51.36		1932.	
	D:				
ROOT MEAN SQUARE		0.00	59.69	39.37	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: 2.00" TH FORGING
 SPECIMEN TYPE: DCB
 ORIENTATION: L-T
 STRESS RATIO: +0.02
 FREQUENCY:

YIELD STRENGTH: 127.0- 145.0 KSI
 ULT. STRENGTH: 190.0- 198.0 KSI
 SPECIMEN THK: 0.750"
 SPECIMEN WIDTH: 5.500"
 REFERENCES: 04300

TITAN.
 ALLOY

TI-6AL-
 4V

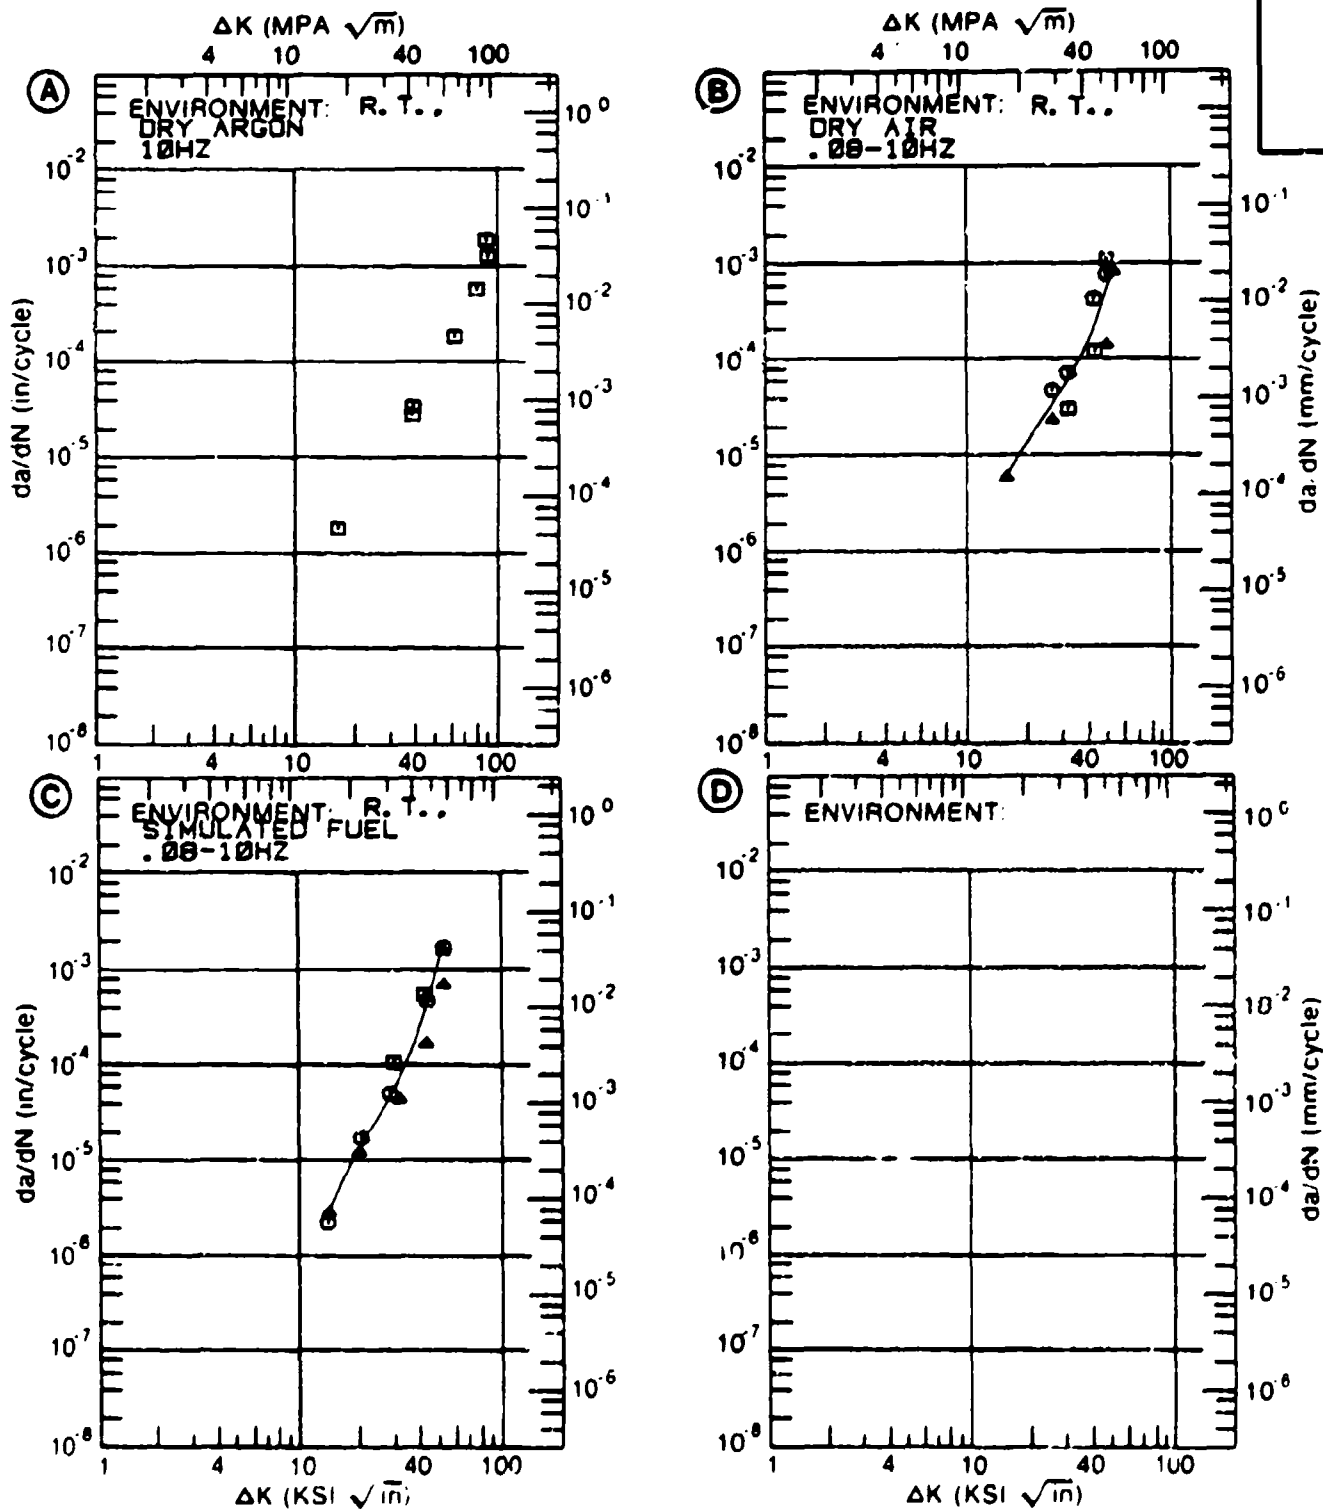


Figure 4.11.3.61

TABLE 4.11.3.62

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.62 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. DIST. WATER 10HZ	E= R. T. 3.5% NAACL 1-10HZ		
DELTA K	A:				
MIN	B:	21.94	13.3		
	C:				
	D:				
		25.00	29.1		
		30.00	61.4		
		35.00	93.1		
		40.00	123.		
		50.00	197.		
		60.00	342.		
		70.00	694.		
		80.00	1657.		
DELTA K	A:				
MAX	B:	82.01	2010.		
	C:				
	D:				
ROOT MEAN SQUARE		0.00	41.05		
PERCENT ERROR					
LIFE		0.0-0.5			
PREDICTION		0.5-0.8			
RATIO		0.8-1.25			
SUMMARY		1.25-2.0			
(NP/NA)		>2.0			

CONDITION/HT: MA
 FORM: 2.00" TH FORGING
 SPECIMEN TYPE: DCB
 ORIENTATION: L-T
 STRESS RATIO: +0.02
 FREQUENCY:

YIELD STRENGTH: 145.0 KSI
 ULT. STRENGTH: 156.0 KSI
 SPECIMEN THK: 0.750- 0.875"
 SPECIMEN WIDTH: 5.500"
 REFERENCES: 04360

TITAN.
 ALLOY

TI-6AL-
 4V

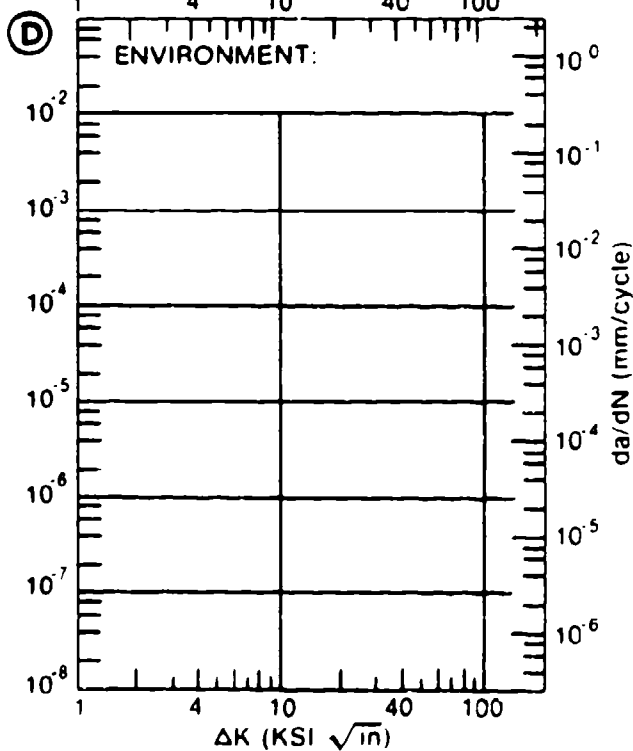
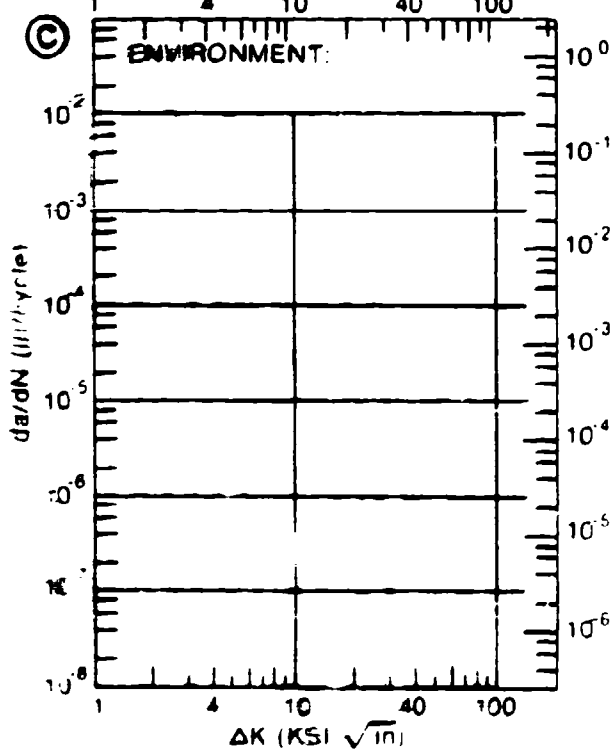
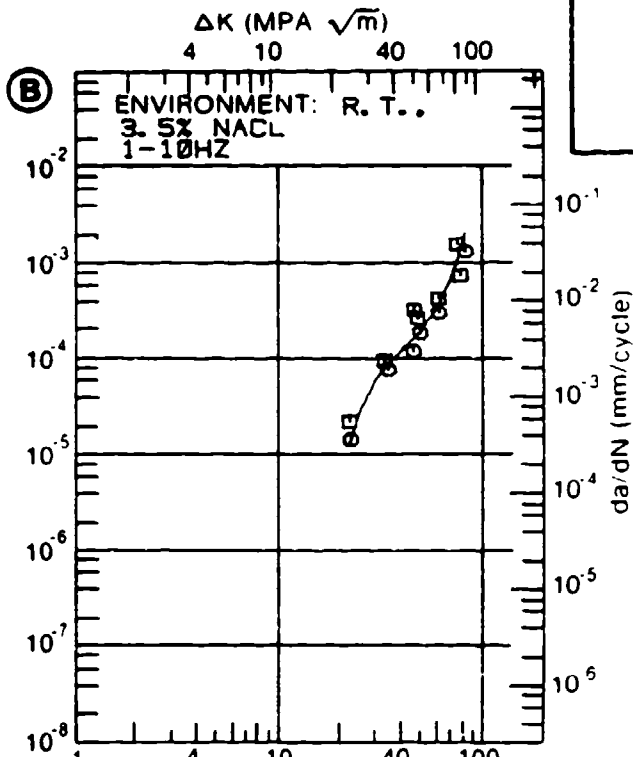
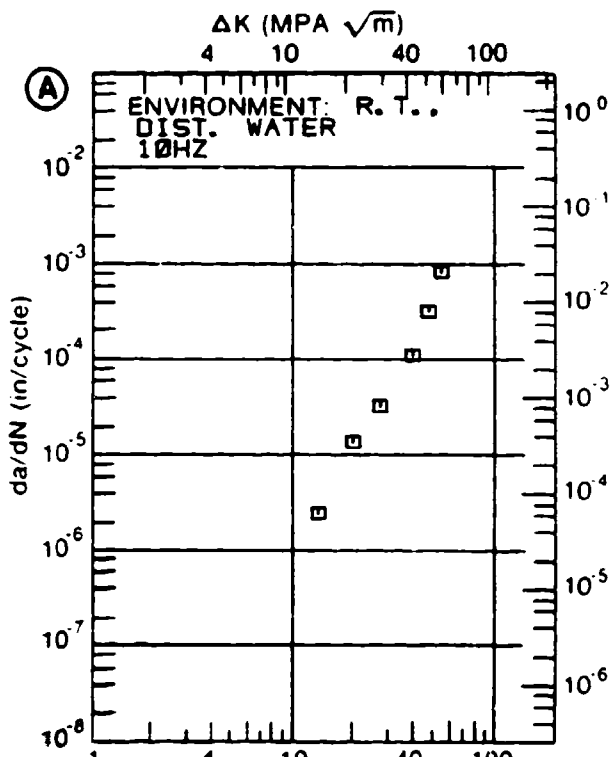


Figure 4.11.3.62

TABLE 4.11.3.63

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.63 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN. /CYCLE)			
		A	B	C	D
		R=+0.02			
DELTA K MIN	A: 18.15	6.34			
	B:				
	C:				
	D:				
	20.00	8.18			
	25.00	15.7			
	30.00	29.2			
35.00	53.0				
40.00	95.0				
50.00	292.				
60.00	857.				
DELTA K MAX	A: 60.61	914.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		13.19			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: 4.50" TH FORGING
 SPECIMEN TYPE: WDL
 ORIENTATION: L-T
 FREQUENCY: 1.00- 30.00 HZ
 ENVIRONMENT: R.T., LAB AIR

YIELD STRENGTH: 130.0 KSI
 ULT. STRENGTH: 139.0 KSI
 SPECIMEN THK: 0.553- 0.555"
 SPECIMEN WIDTH: 4.999- 5.000"
 REFERENCES: MA002

TITAN.
 ALLOY

TI-6AL-
 4V

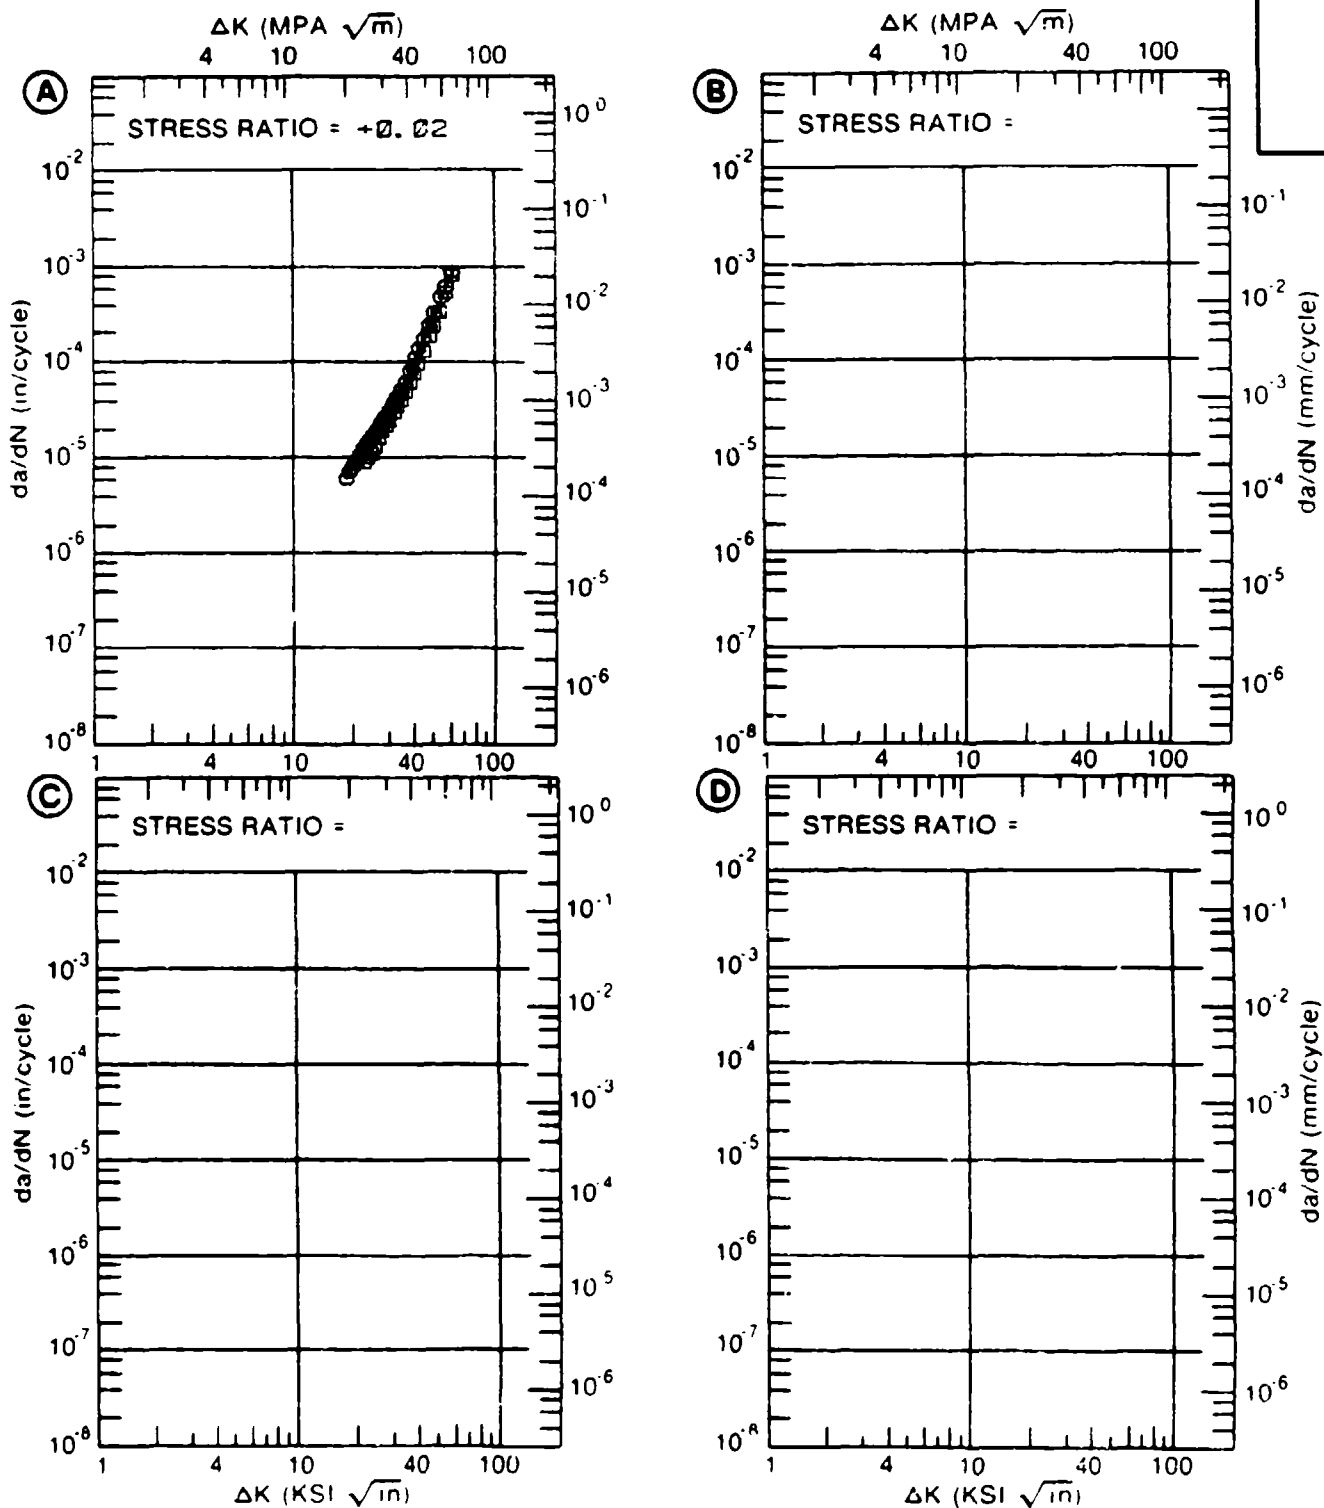


Figure 4.11.3.63

TABLE 4.11.3.64

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.64 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA		1300F 2HRS AC			
ENVIRONMENT: + 300F, AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.00	R=+0.25	R=+0.54	
DELTA K	A: 10.32	.610			
MIN	B: 10.79		1.01		
	C: 7.74			.589	
	D:				
	8.00			.621	
	9.00			.925	
	10.00			1.19	
	12.00	1.29	2.58	3.77	
	16.00	2.79	6.11	9.69	
	20.00	6.72	13.5		
	25.00	16.1	28.1		
	30.00	31.4			
	35.00	52.2			
	40.00	76.6			
DELTA K	A: 44.22	97.8			
MAX	B: 27.30		37.7		
	C: 19.93			20.8	
	D:				
ROOT MEAN SQUARE		20.23	28.07	43.68	
PERCENT ERROR					
LIFE	0.0-0.8				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA 1300F 2HRS AC
 FORM: 1.75" TH DISK
 SPECIMEN TYPE: KB BAR
 ORIENTATION: L-R
 FREQUENCY: 0.33 HZ
 ENVIRONMENT: + 300° F, AIR

YIELD STRENGTH: 120.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.244- 0.250"
 SPECIMEN WIDTH: 1.000- 1.005"
 REFERENCES: GE007

TITAN.
 ALLOY

TI-6AL-
 4V

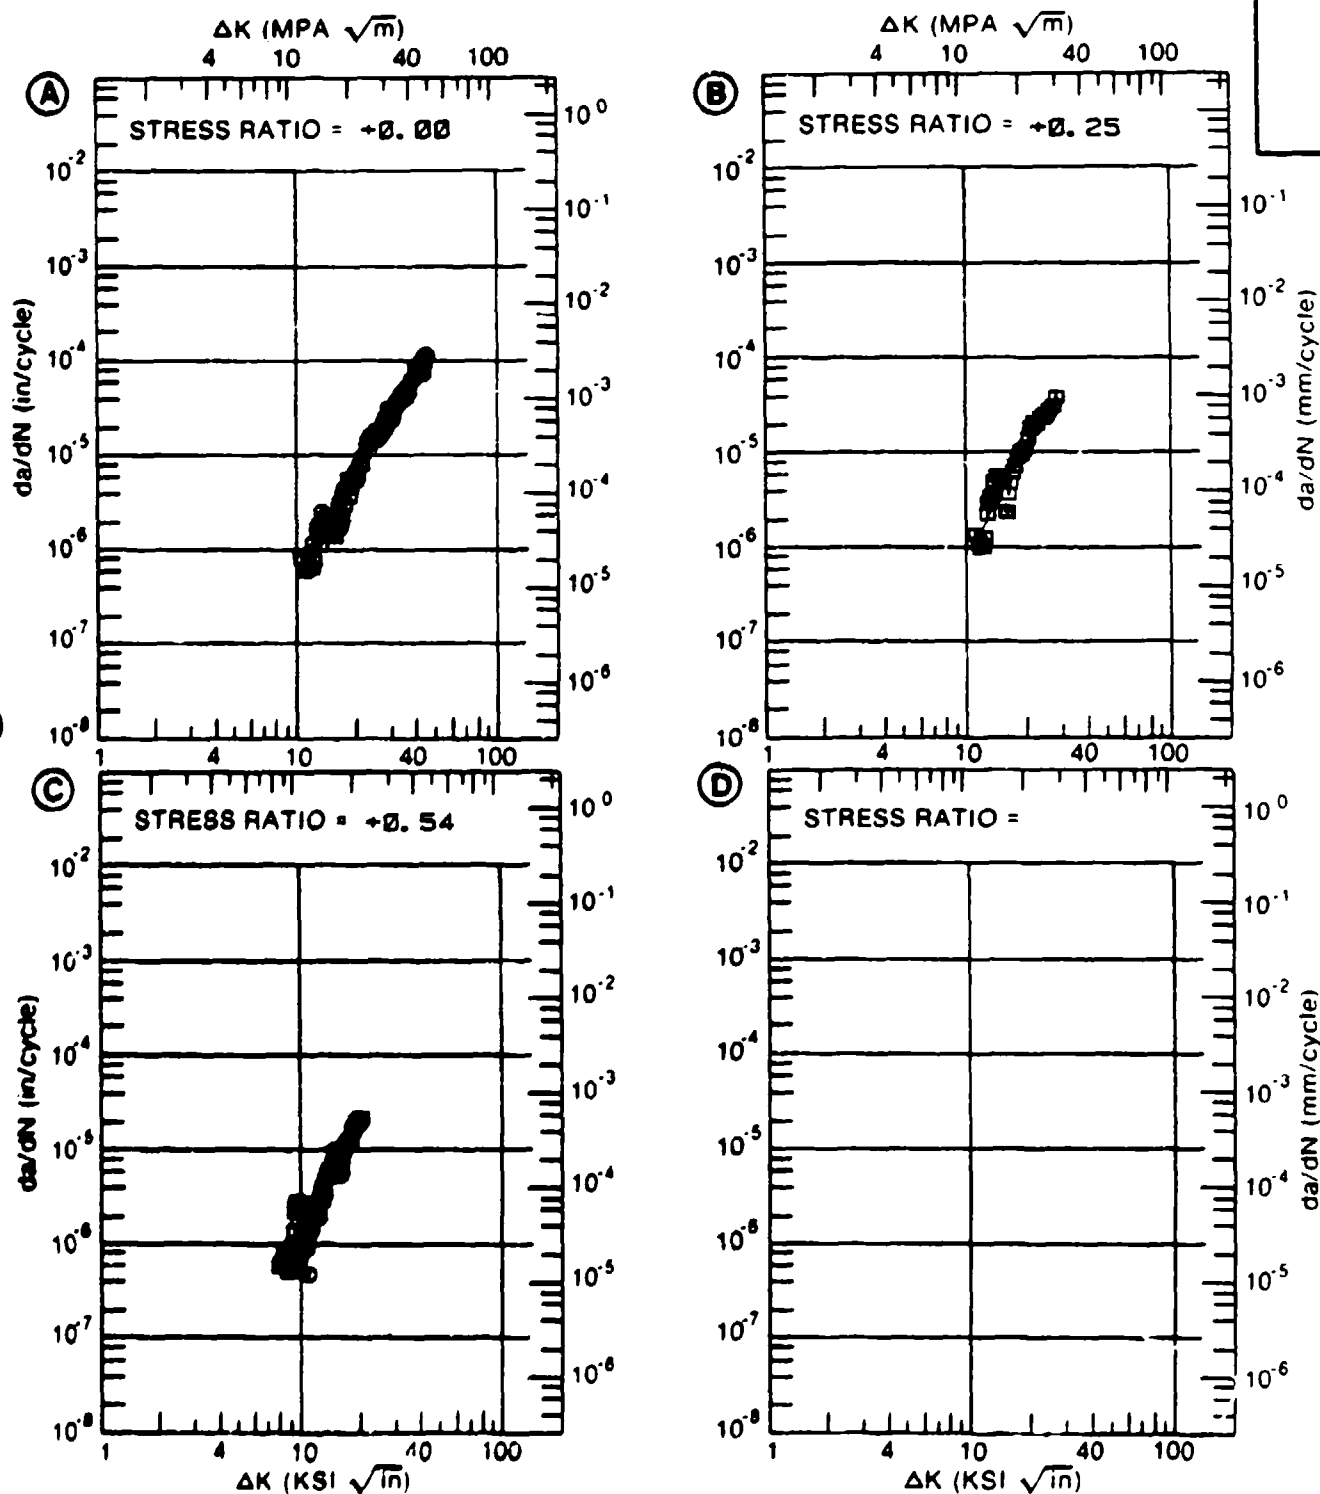


Figure 4.11.3.64

TABLE 4.11.3.65

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.65 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: MA 1300F 2HRS AC
ENVIRONMENT: + 600F, AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.00	R=+0.25	R=+0.54	
DELTA K MIN	A: 10.19	1.49			
	B: 8.78		1.23		
	C: 8.13			.684	
	D:				
	9.00		1.21	.964	
	10.00		1.24	1.46	
	13.00	2.32	2.08	4.75	
	16.00	3.90	4.36	12.4	
	20.00	7.83	11.2	30.9	
	25.00	18.0	28.1		
	30.00	39.4			
	35.00	81.4			
	40.00	160.			
DELTA K MAX	A: 41.78	202.			
	B: 28.82		46.2		
	C: 20.36			32.9	
	D:				
ROOT MEAN SQUARE		21.78	23.65	26.02	
PERCENT ERROR					

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: MA 1300F 2HRS AC
 FORM: 1.75" TH FORWARD SPOOL
 SPECIMEN TYPE: KB BAR
 ORIENTATION: L-R
 FREQUENCY: 0.33 HZ
 ENVIRONMENT: + 800° F. AIR

YIELD STRENGTH: 120.0 KSI
 ULT STRENGTH:
 SPECIMEN THK: 0.249- 0.253"
 SPECIMEN WIDTH: 0.995- 1.003"
 REFERENCES: GE007

TITAN.
 ALLOY
 TI-6AL-
 4V

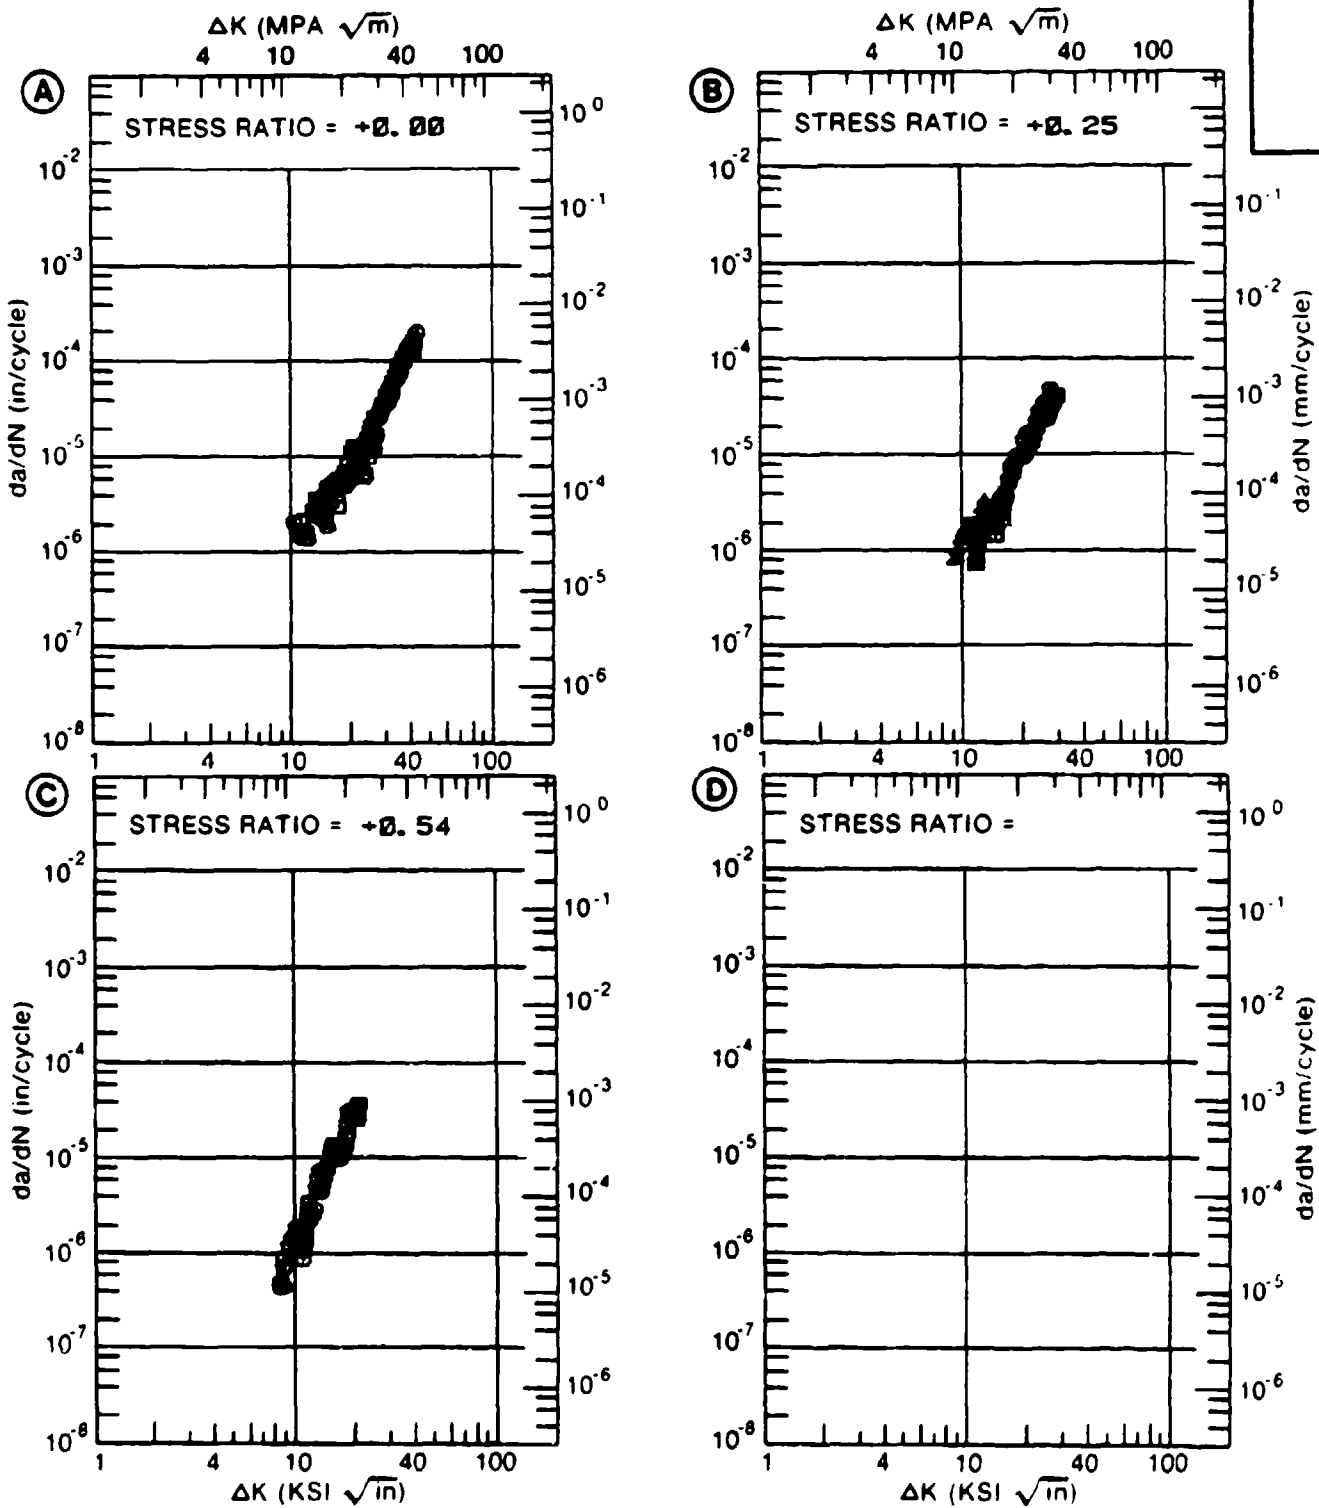


Figure 4.11.3.65

TABLE 4.11.3.66

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.66 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K	A: 8.50	2.47			
MIN	B: 4.86		.285		
	C:				
	D:				
	5.00		.326		
	6.00		.698		
	7.00		1.21		
	8.00		1.85		
	9.00	2.81	2.65		
	10.00	3.57	3.63		
	13.00	6.80	8.44		
	16.00	12.0	19.2		
	20.00	23.8	64.9		
	25.00	51.4			
	30.00	105.			
	35.00	203.			
	40.00	378.			
DELTA K	A: 42.13	487.			
MAX	B: 22.81		169.		
	C:				
	D:				
ROOT MEAN SQUARE		8.97	13.03		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 0.13" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 149.1- 149.2 KSI
 ULT. STRENGTH: 156.2 KSI
 SPECIMEN THK: 0.124- 0.125"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90981

TITAN.
 ALLOY
 TI-6AL-
 4V

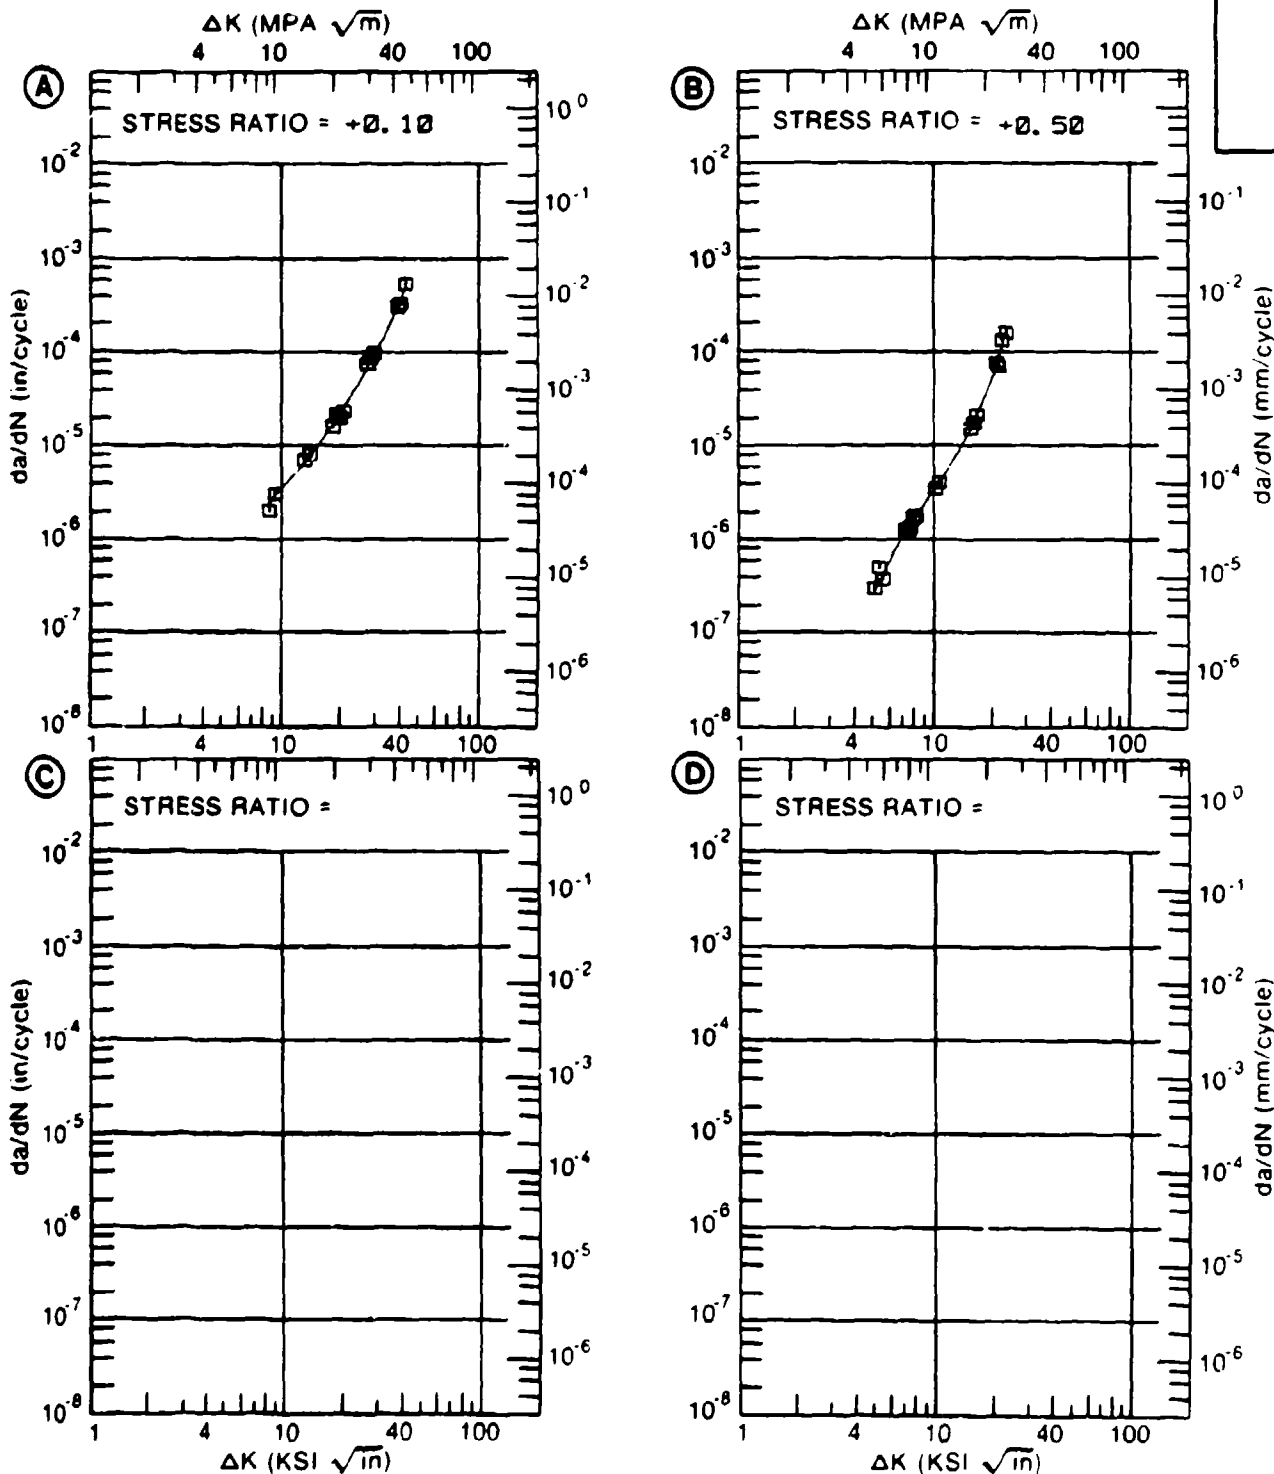


Figure 4.11.3.66

TABLE 4.11.3.67

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.67 INDICATING EFFECT
OF FREQUENCY

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
ENVIRONMENT: R. T. , 3.5% NaCl					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		F(HZ)= 0.10		F(HZ)= 10.00	
DELTA K MIN	A: 8.36	2.00			
	B: 8.72		2.33		
	C:				
	D:				
	9.00	2.47	2.79		
	10.00	3.50	4.86		
	13.00	9.45	15.6		
	16.00	21.1	32.6		
	20.00	44.7	63.0		
	25.00	74.0	111.		
	30.00		168.		
	35.00		237.		
	40.00		321.		
DELTA K MAX	A: 26.41	79.4			
	B: 42.50		370.		
	C:				
	D:				
ROOT MEAN SQUARE		9.04	9.11		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5	1	1		
	0.5-0.8				
	0.8-1.25				
	1.25-2.0				
	>2.0				

CONDITION/HT: RA
 FORM: 0.13" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: +0.10
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 149.2 KSI
 ULT. STRENGTH: 156.2 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90981

TITAN.
 ALLOY

TI-6AL-
 4V

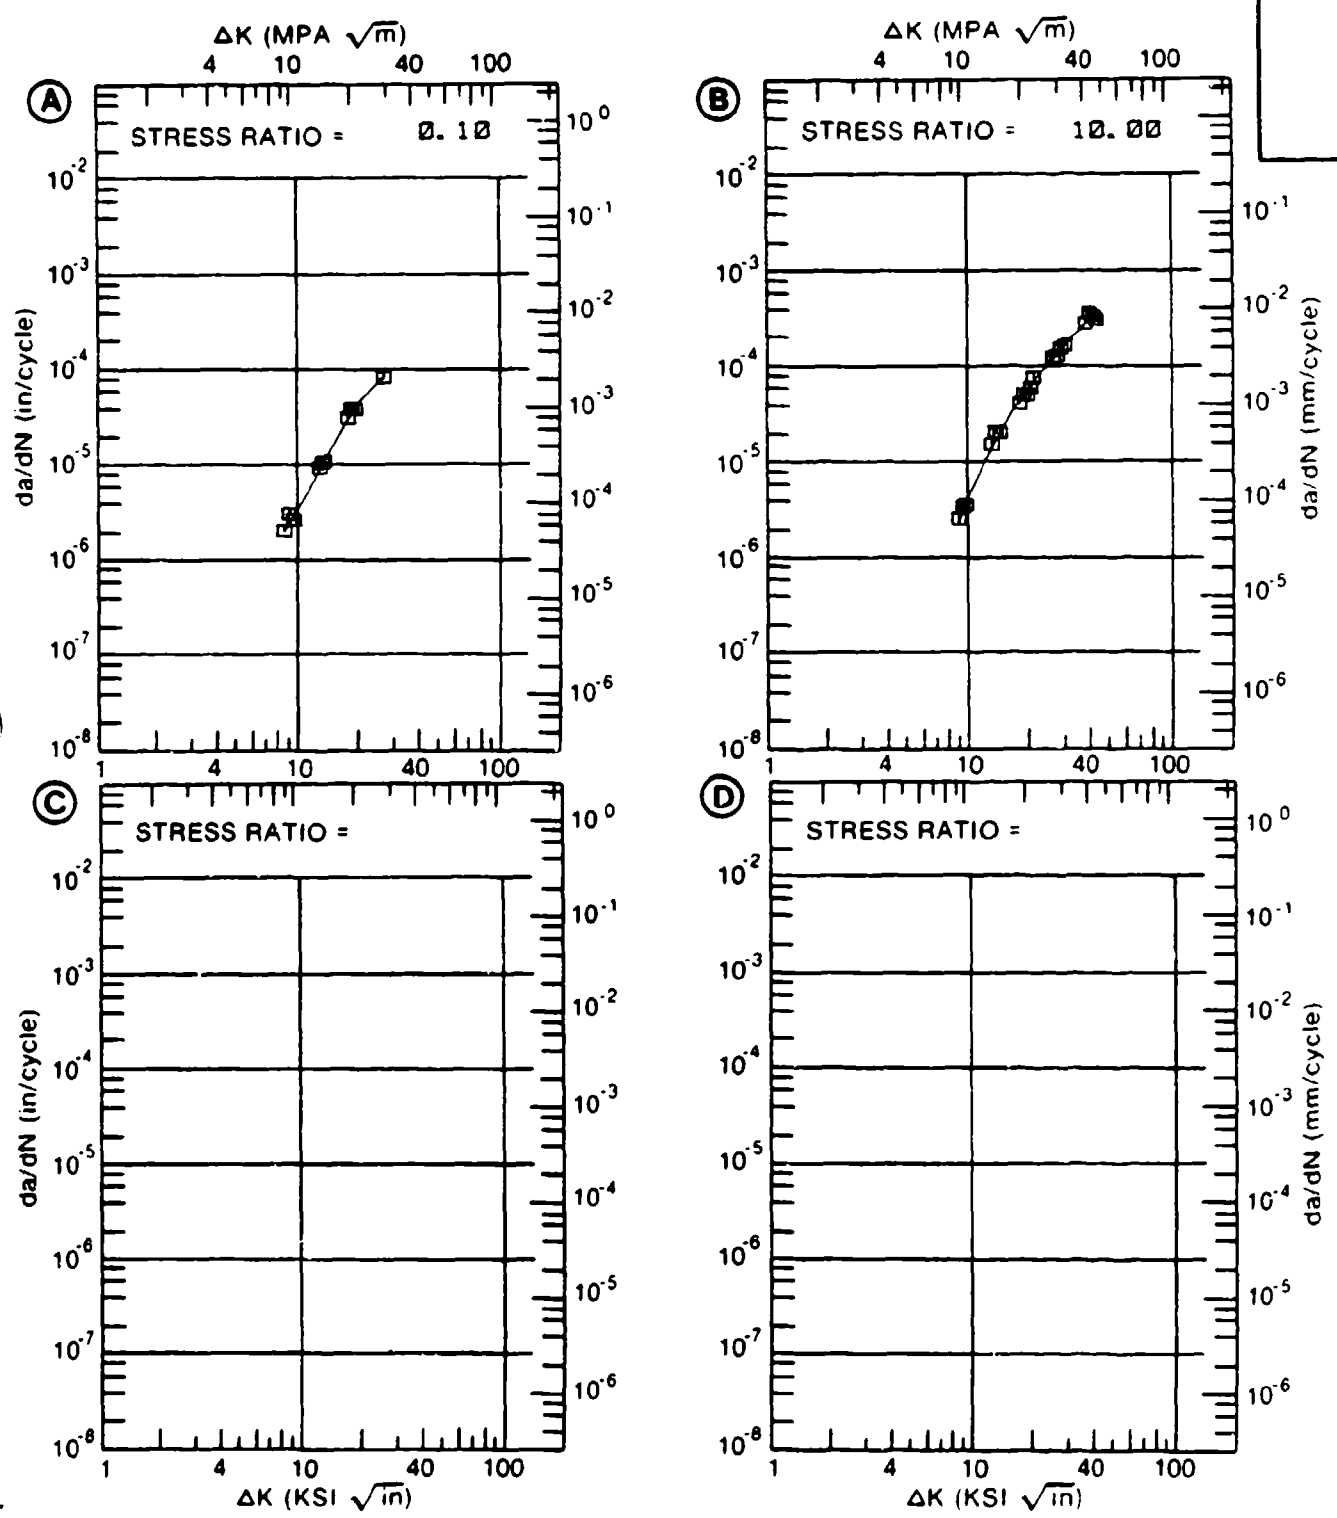


Figure 4.11.3.67

TABLE 4.11.3.68

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.68 INDICATING EFFECT
OF FREQUENCY

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
ENVIRONMENT: R. T. , HUMID AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		F(HZ)= 10.00			
DELTA K	A: 8.50	.637			
MIN	B:				
	C:				
	D:				
	9.00	.792			
	10.00	1.18			
	13.00	3.12			
	16.00	6.30			
	20.00	12.1			
	25.00	19.9			
	30.00	26.1			
	35.00	29.2			
DELTA K	A: 37.14	29.6			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		12.83			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: L-S
 STRESS RATIO: +0.10
 ENVIRONMENT: R. T., HUMID AIR

YIELD STRENGTH: 119.1 KSI
 ULT. STRENGTH: 139.1 KSI
 SPECIMEN THK: 0.376"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90001

TITAN.
 ALLOY

TI-6AL-
 4V

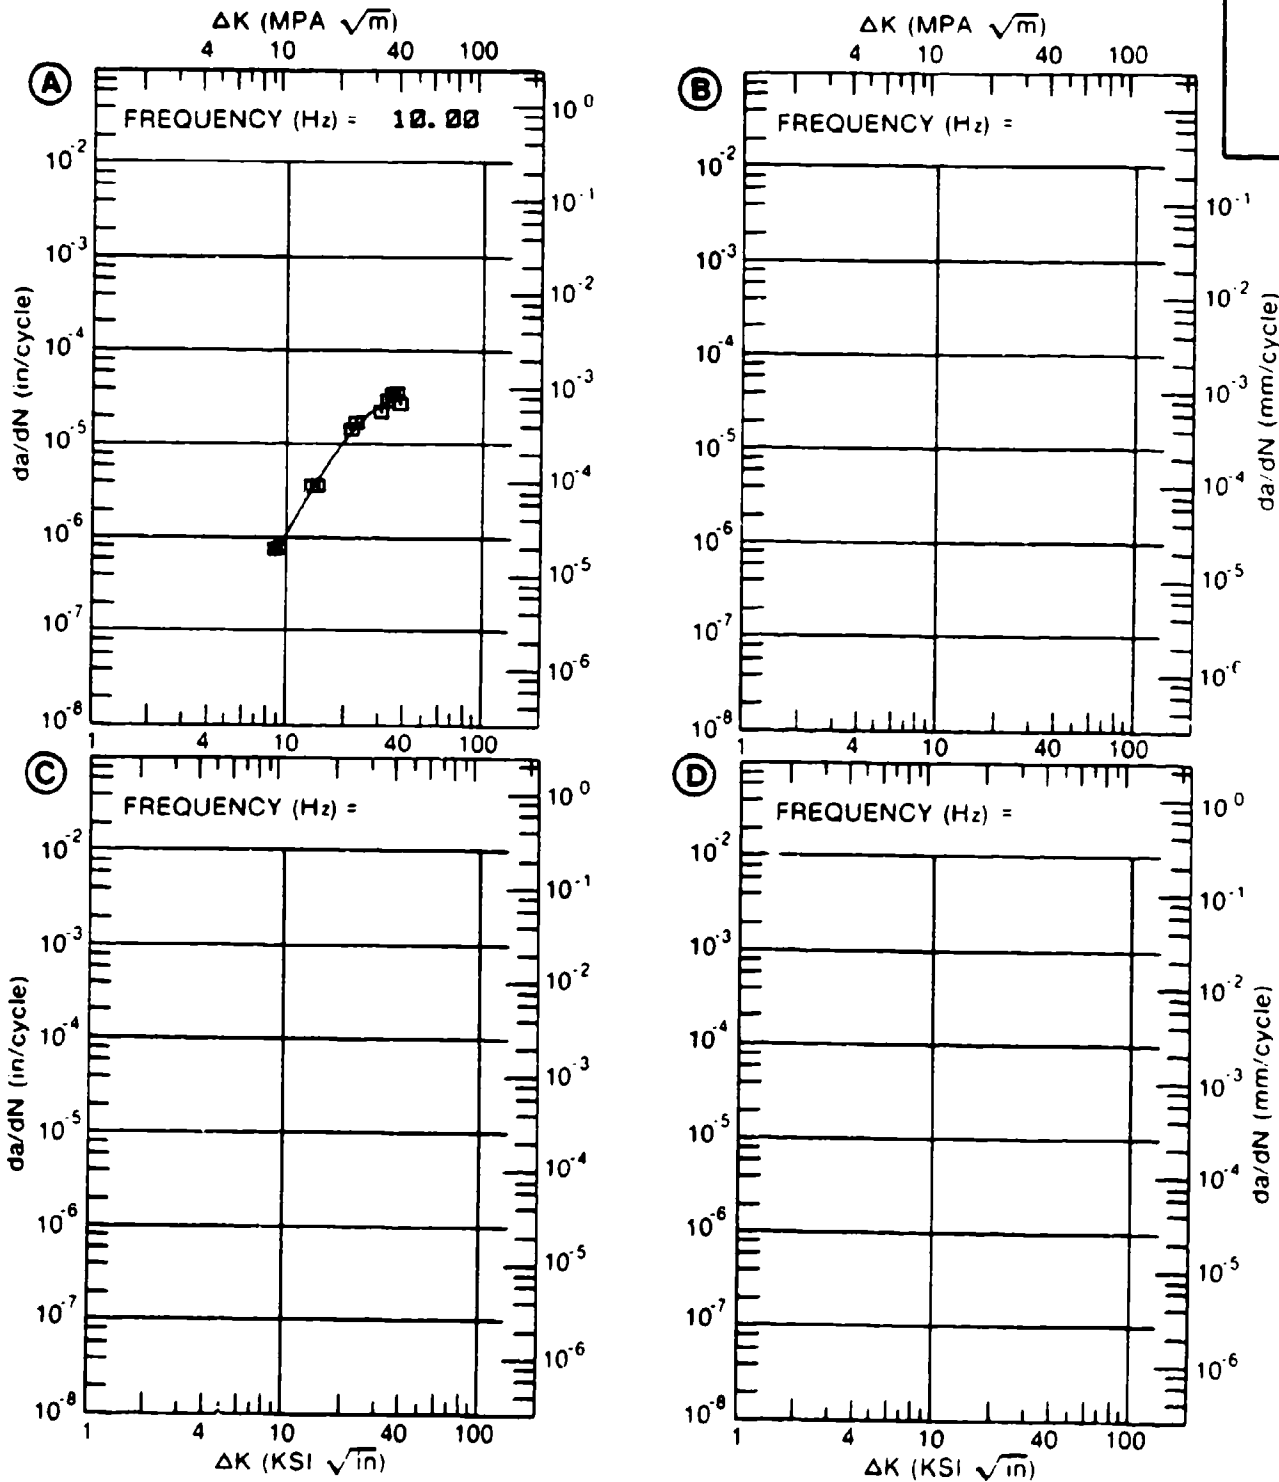


Figure 4.11.3.68

TABLE 4.11.3.69

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.69 INDICATING EFFECT
OF FREQUENCY

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: RA
ENVIRONMENT: R. T. , 3.5% NaCl

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		F(HZ)= 10.00			
DELTA K MIN	A: 15.77	37.3			
	B:				
	C:				
	D:				
	16.00	37.9			
	20.00	49.7			
	25.00	67.2			
	30.00	84.6			
	35.00	99.2			
DELTA K MAX	A: 35.80	101.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		22.70			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 STRESS RATIO: +0.10
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 141.7 KSI
 ULT STRENGTH: 151.9 KSI
 SPECIMEN THK: 0.377"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90981

TITAN.
 ALLOY

TI-6AL-
 4V

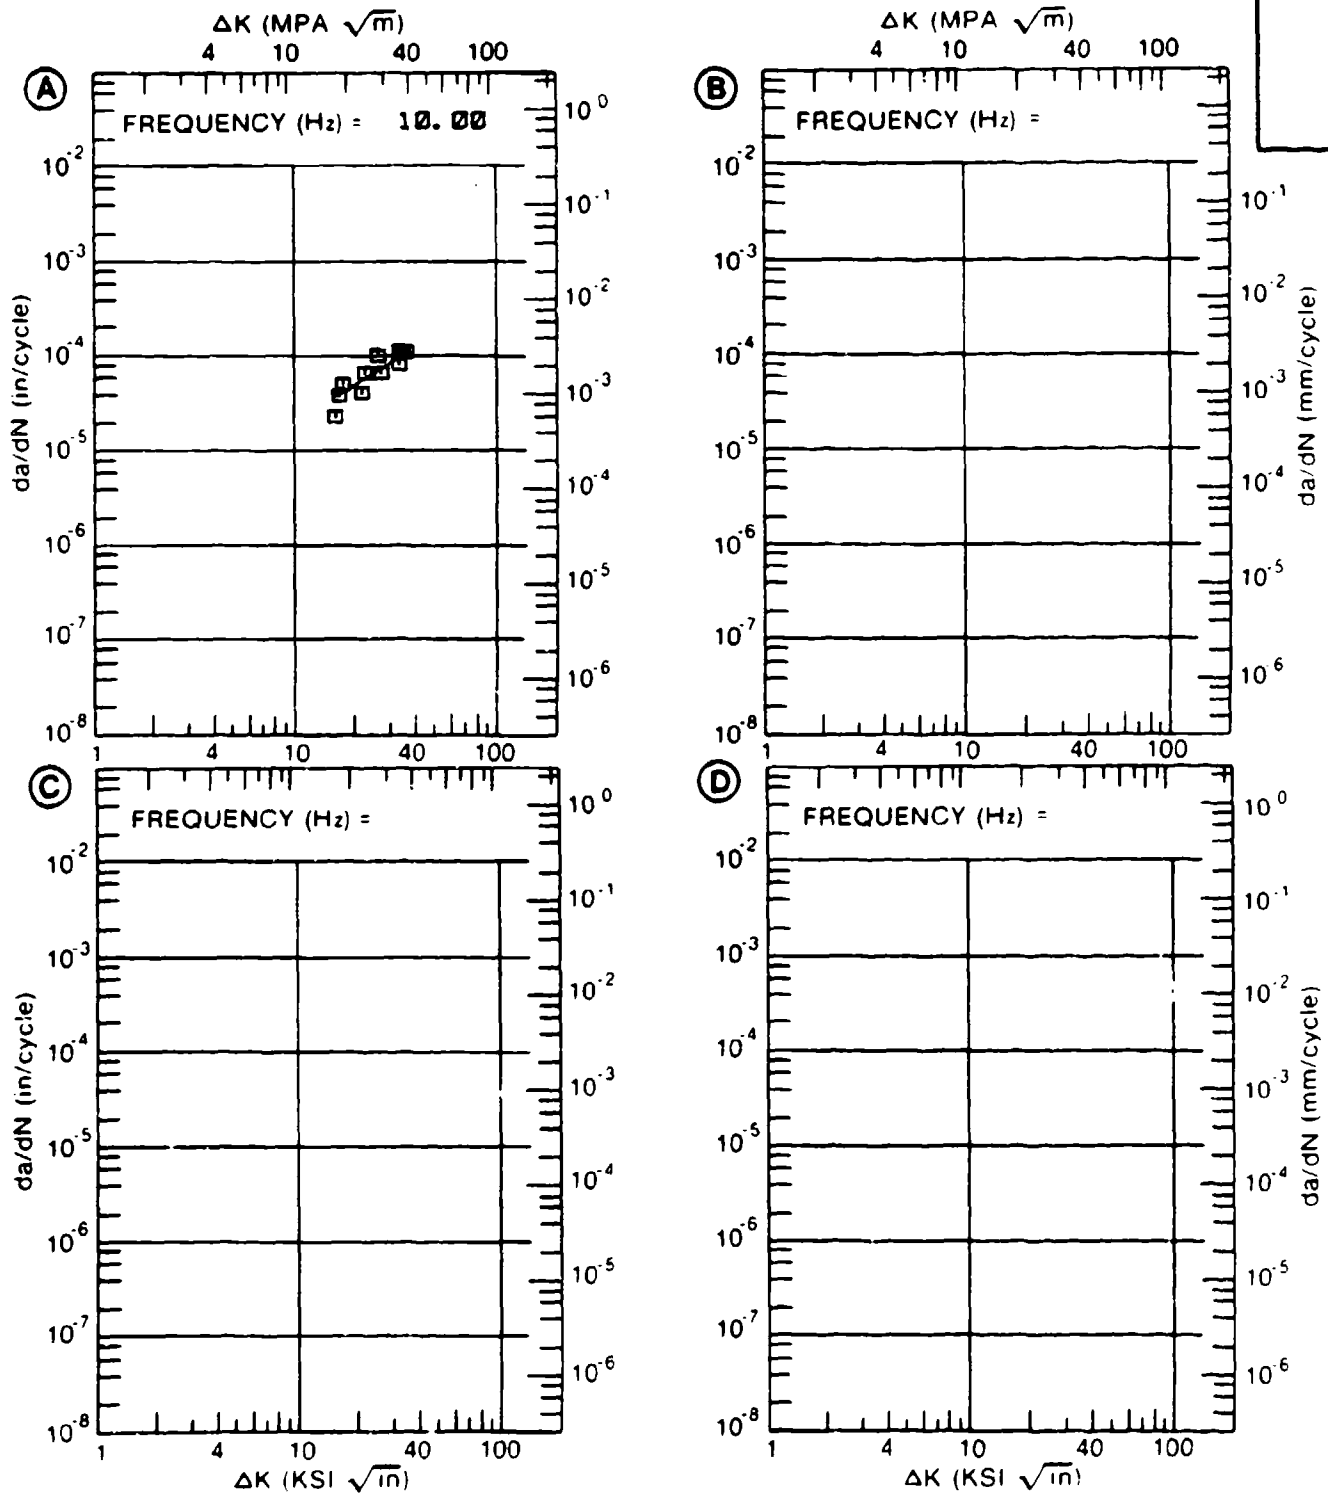


Figure 4.11.3.69

TABLE 4.11.3.70

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.70 INDICATING EFFECT
OF STRESS RATIO

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K	A: 10.10	4.77			
MIN	B: 5.41		.99		
	C:				
	D:				
	6.00		1.54		
	7.00		2.63		
	8.00		3.84		
	9.00		5.12		
	10.00		6.45		
	13.00	6.51	10.9		
	16.00	9.27	16.7		
	20.00	14.4	26.8		
	25.00	23.2			
DELTA K	A: 28.25	27.0			
MAX	B: 23.27		33.7		
	C:				
	D:				
ROOT MEAN SQUARE		5.20	12.89		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 141.7 KSI
 ULT. STRENGTH: 151.8 KSI
 SPECIMEN THK: 0.370- 0.371"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90981

TITAN.
 ALLOY
 TI-6AL-
 4V

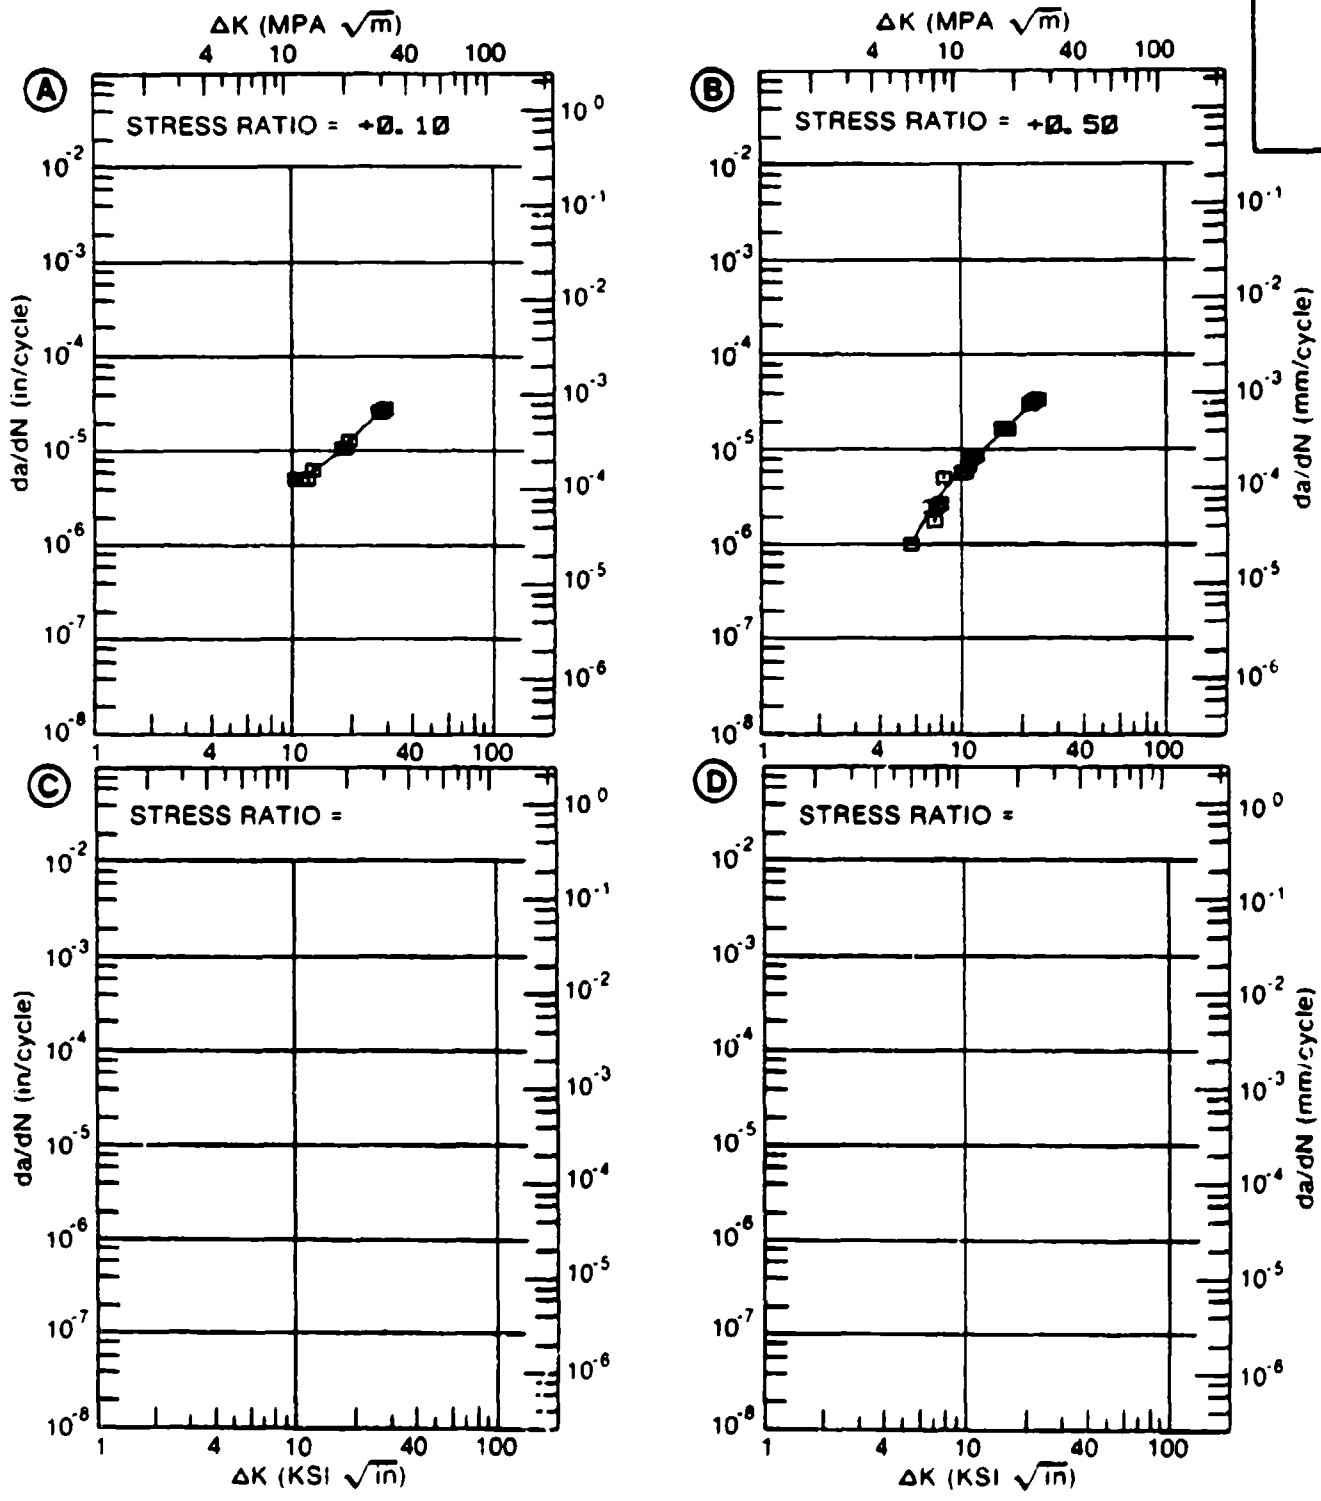


Figure 4.11.3.70

TABLE 4.11.3.71

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.71 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
ENVIRONMENT: R. T. , 3.5% NaCl					
DELTA K (KSI*IN ^{1/2})		DA/DN (10 ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K MIN	A: 17.57	35.8	15.2		
	B: 6.24				
	C:				
	D:				
	7.00		15.8		
	8.00		22.0		
	9.00		28.4		
	10.00		33.7		
	13.00		51.4		
	16.00		86.8		
	20.00	58.9	148.		
	25.00	86.0			
	30.00	132.			
	35.00	181.			
	40.00	206.			
DELTA K MAX	A: 42.87	209.	697.		
	B: 23.07				
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		11.25	18.49		
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1		

CONDITION/HT: RA
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 141.7 KSI
 ULT. STRENGTH: 151.8 KSI
 SPECIMEN THK: 0.372"
 SPECIMEN WIDTH: 5.000"
 REFERENCES 90001

TITAN.
 ALLOY

TI-6AL-4V

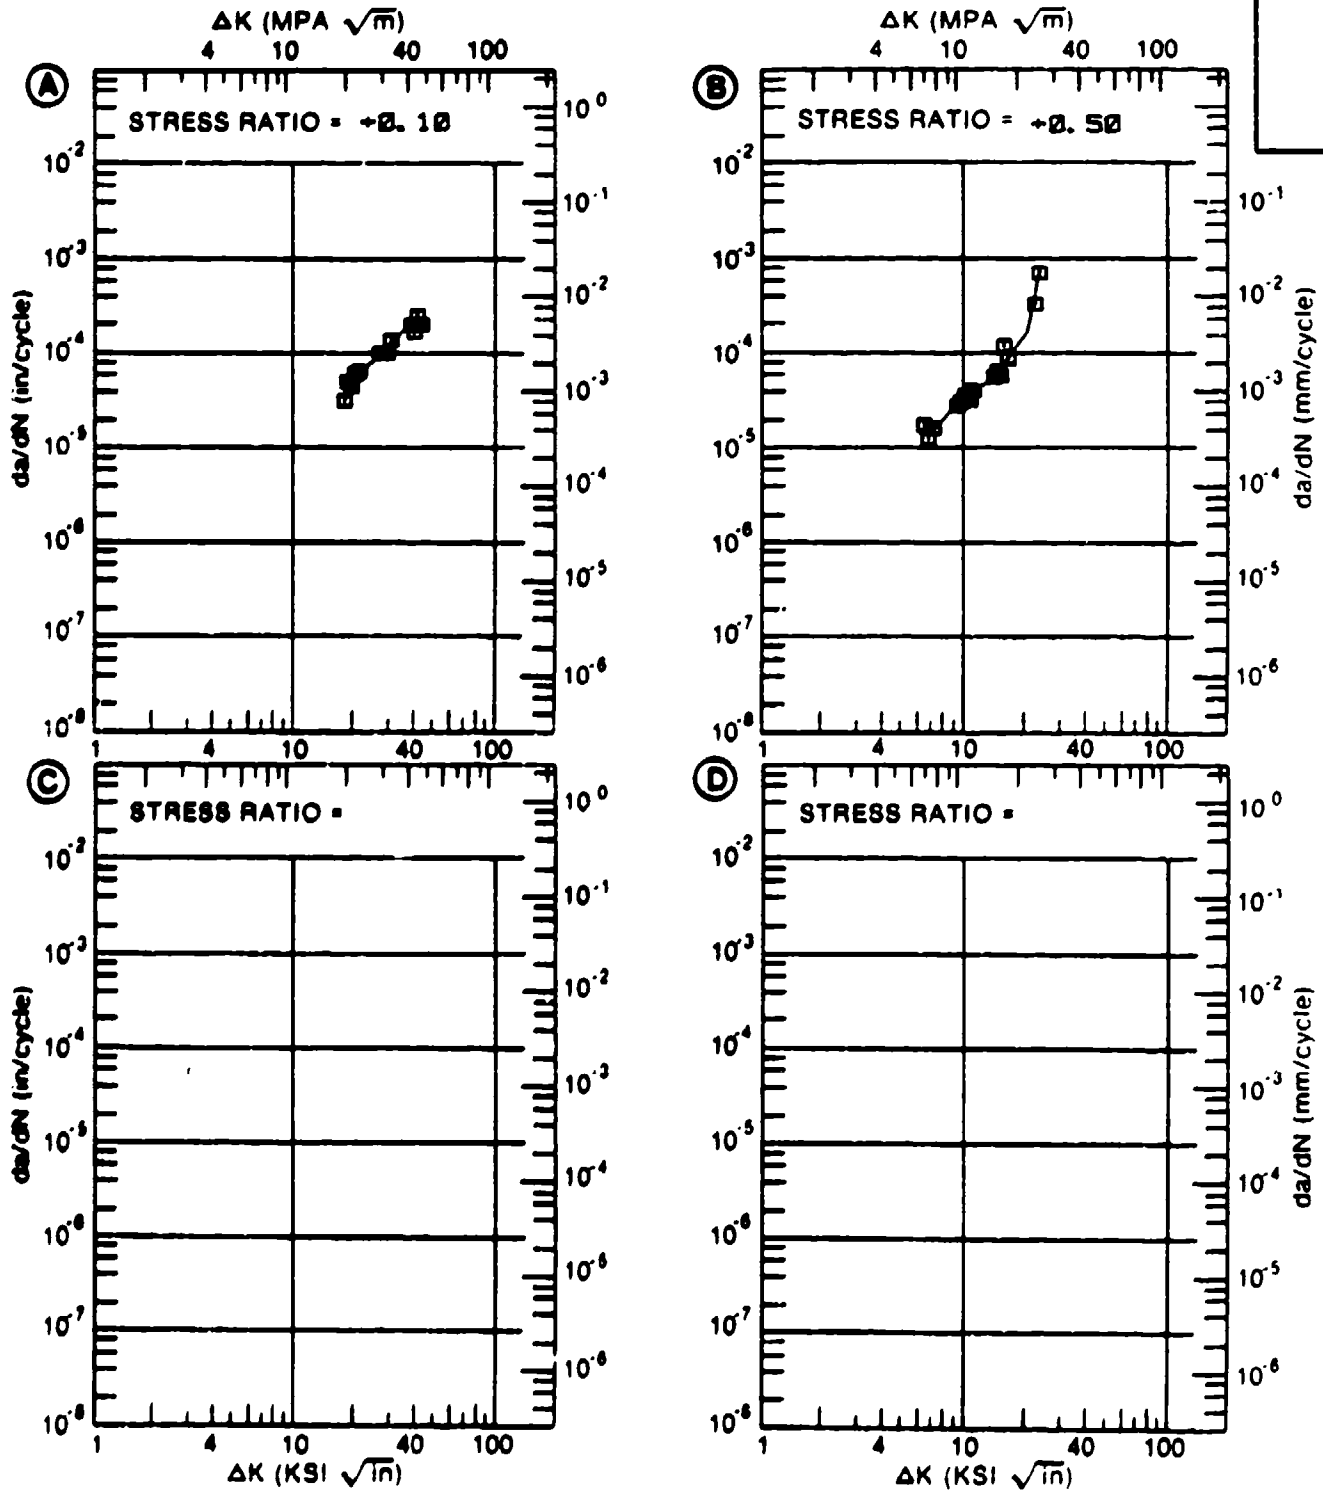


Figure 4.11.3.71

TABLE 4.11.3.72

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.72 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
ENVIRONMENT: R. T. , S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10**6 IN. /CYCLE)			
		A	B	C	D
		R=+0.08			
DELTA K	A: 5.67	.224			
MIN	B:				
	C:				
	D:				
	6.00	.262			
	7.00	.437			
	8.00	.747			
	9.00	1.26			
	10.00	2.08			
	13.00	7.51			
	16.00	19.9			
	20.00	48.7			
DELTA K	A: 23.65	81.2			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		22.66			
PERCENT ERROR					
LIFE	0.0-0.9				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0	1			
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 129.0 KSI
 ULT. STRENGTH: 140.0 KSI
 SPECIMEN THK: 0.410"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 99579

TITAN.
 ALLOY

TI-6AL-4V

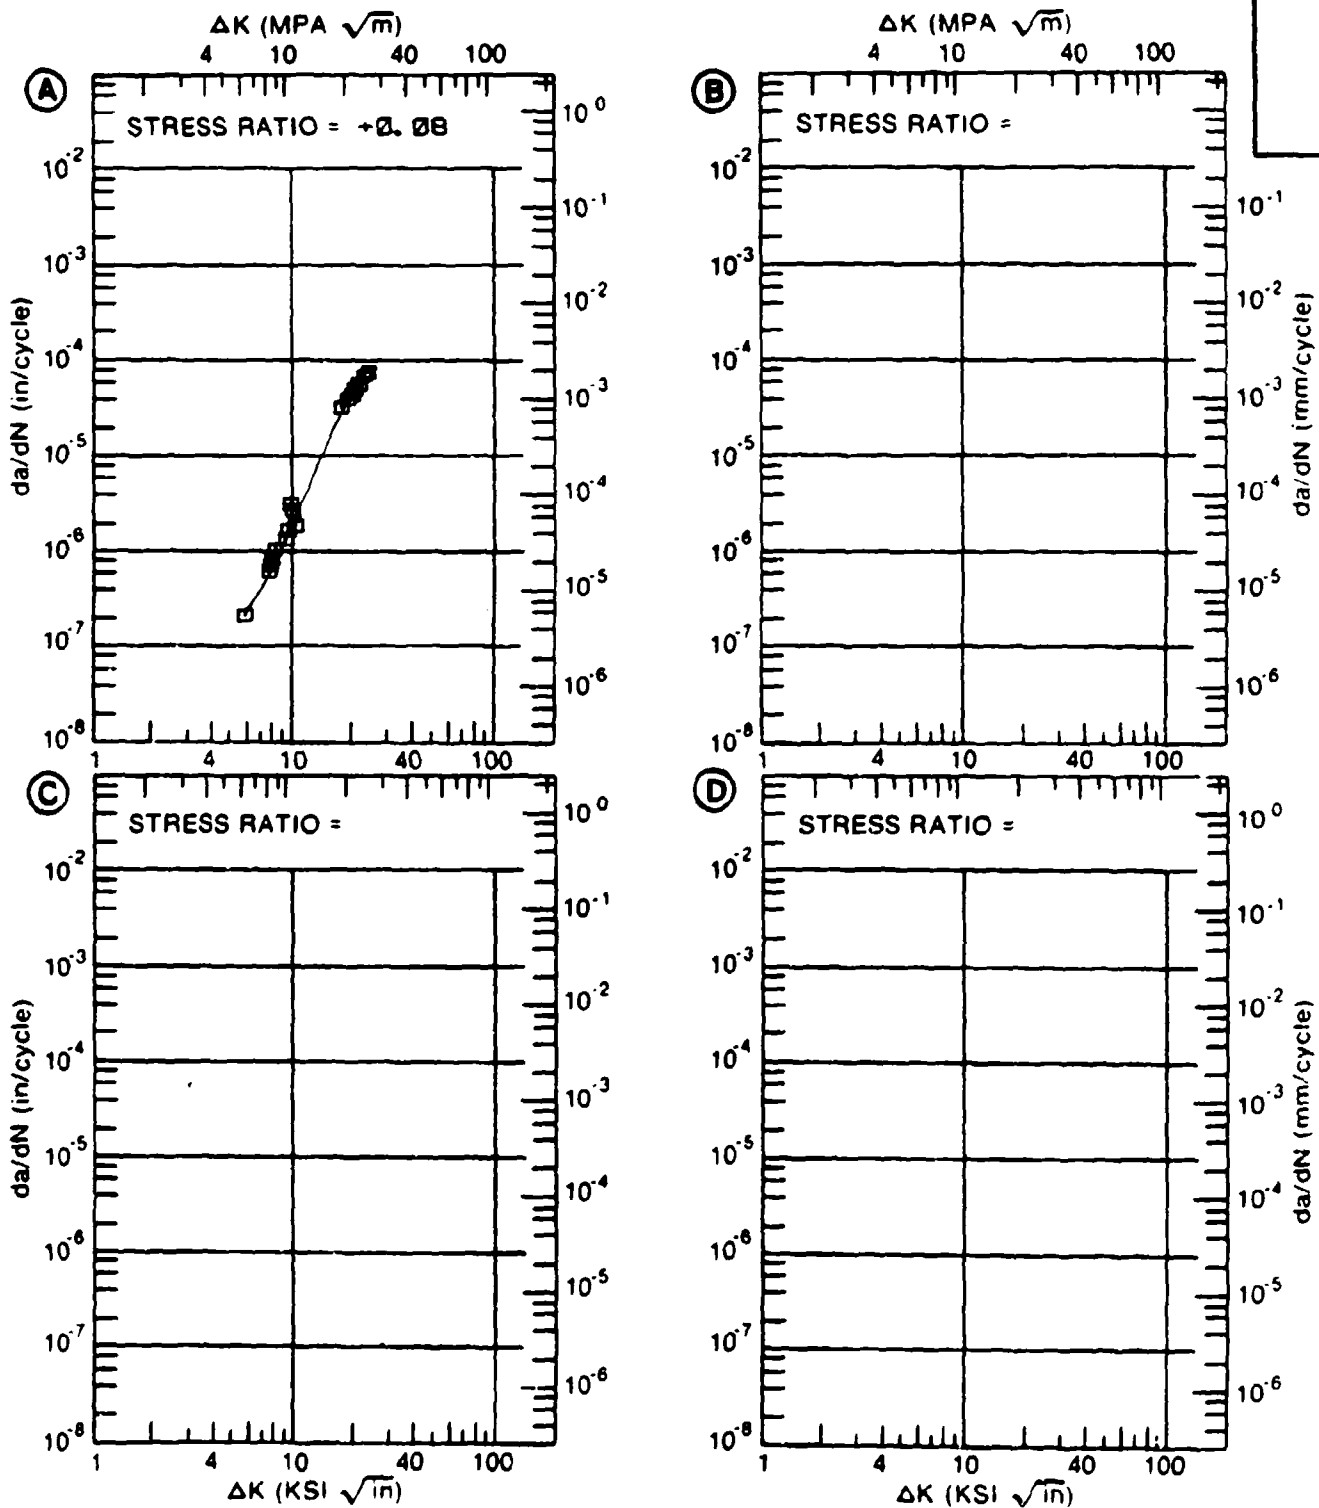


Figure 4.11.3.72

TABLE 4.11.3.73

**FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR**

**DATA ASSOCIATED WITH FIGURE 4.11.3.73 INDICATING EFFECT
OF STRESS RATIO**

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
ENVIRONMENT: R. T. , S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K	A: 29.01	1405.			
MIN	B:				
	C:				
	D:				
	30.00	1418.			
	35.00	1800.			
	40.00	2531.			
	50.00	3951.			
DELTA K	A: 52.51	4043.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		13.89			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 0.10 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 141.7 KSI
 ULT. STRENGTH: 151.8 KSI
 SPECIMEN THK: 0.374- 0.375"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: 90981

TITAN.
 ALLOY

TI-6AL-
 4V

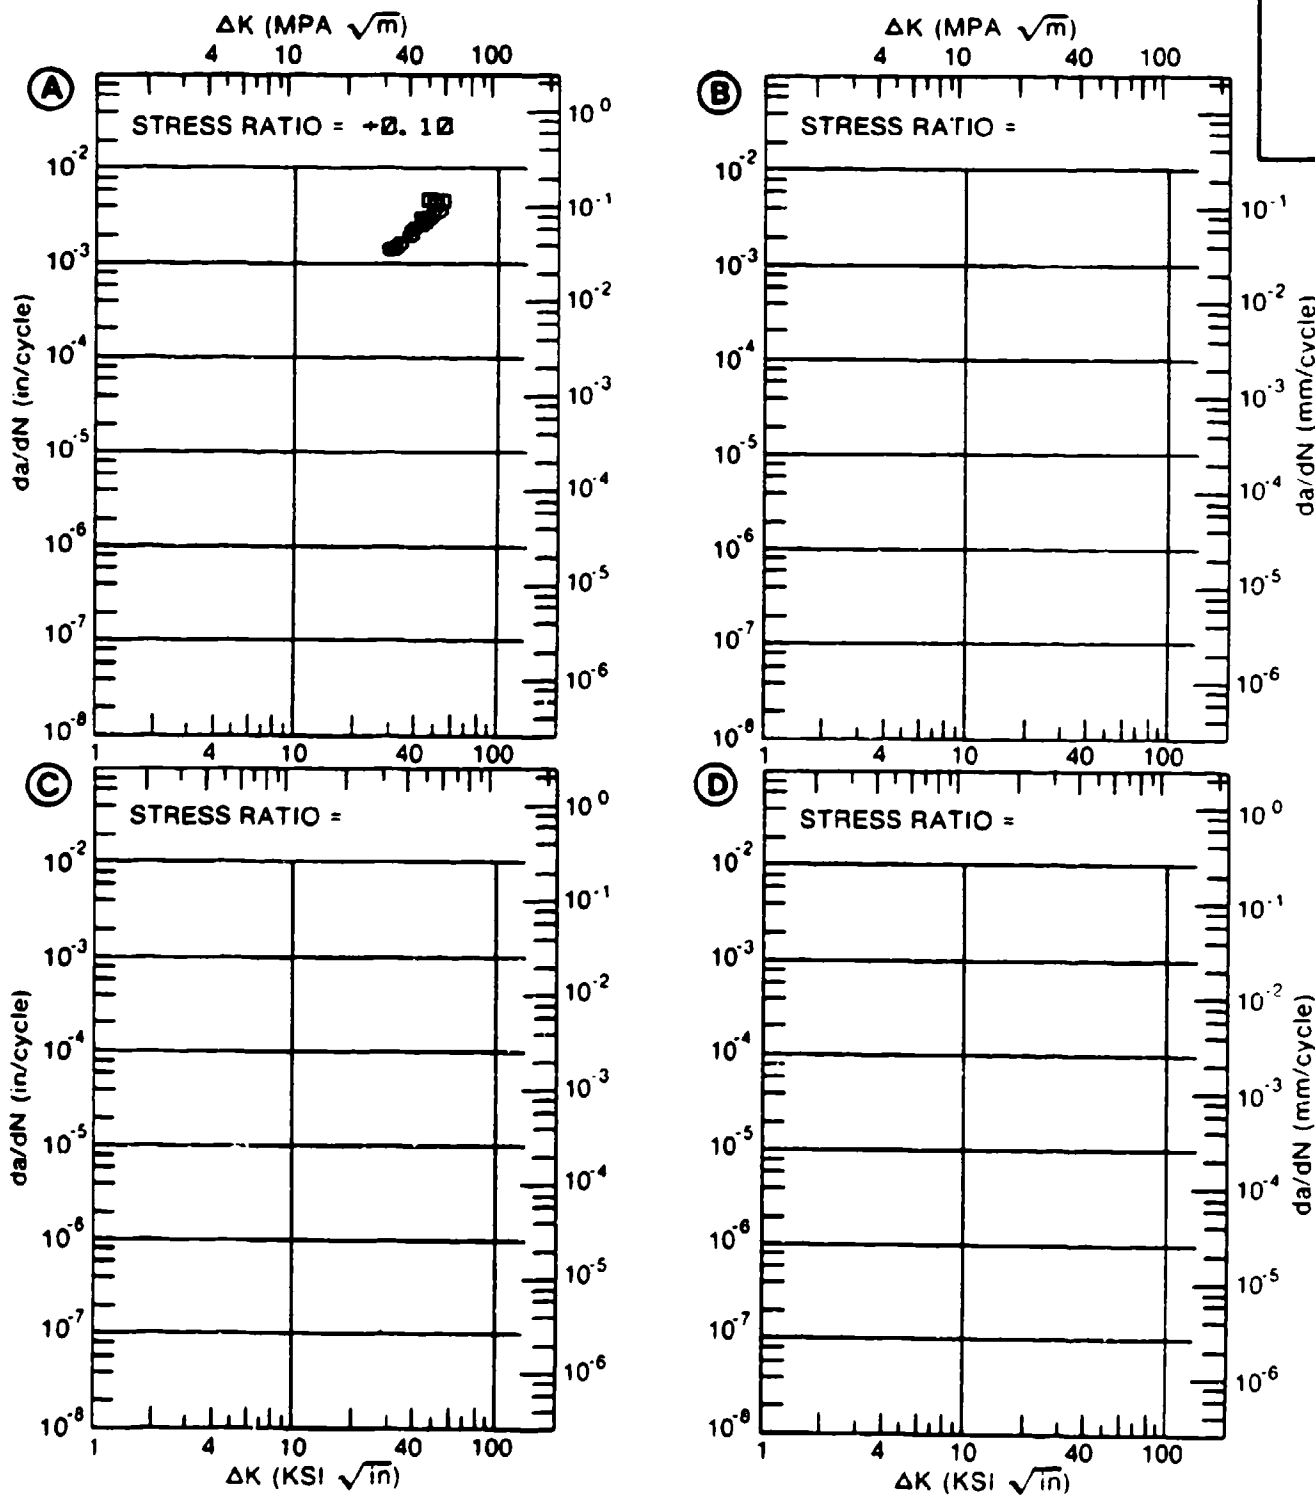


Figure 4.11.3.73

TABLE 4.11.3.74

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.74 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K	A: 13.05	4.93			
MIN	B:				
	C:				
	D:				
	16.00	11.0			
	20.00	21.3			
	25.00	41.9			
	30.00	87.4			
	35.00	205.			
DELTA K	A: 36.63	279.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		9.02			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 0.39" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH: 149.2 KSI
 ULT. STRENGTH: 156.2 KSI
 SPECIMEN THK: 0.372"
 SPECIMEN WIDTH: 2.549"
 REFERENCES: 90991

TITAN.
 ALLOY
 TI-6AL-
 4V

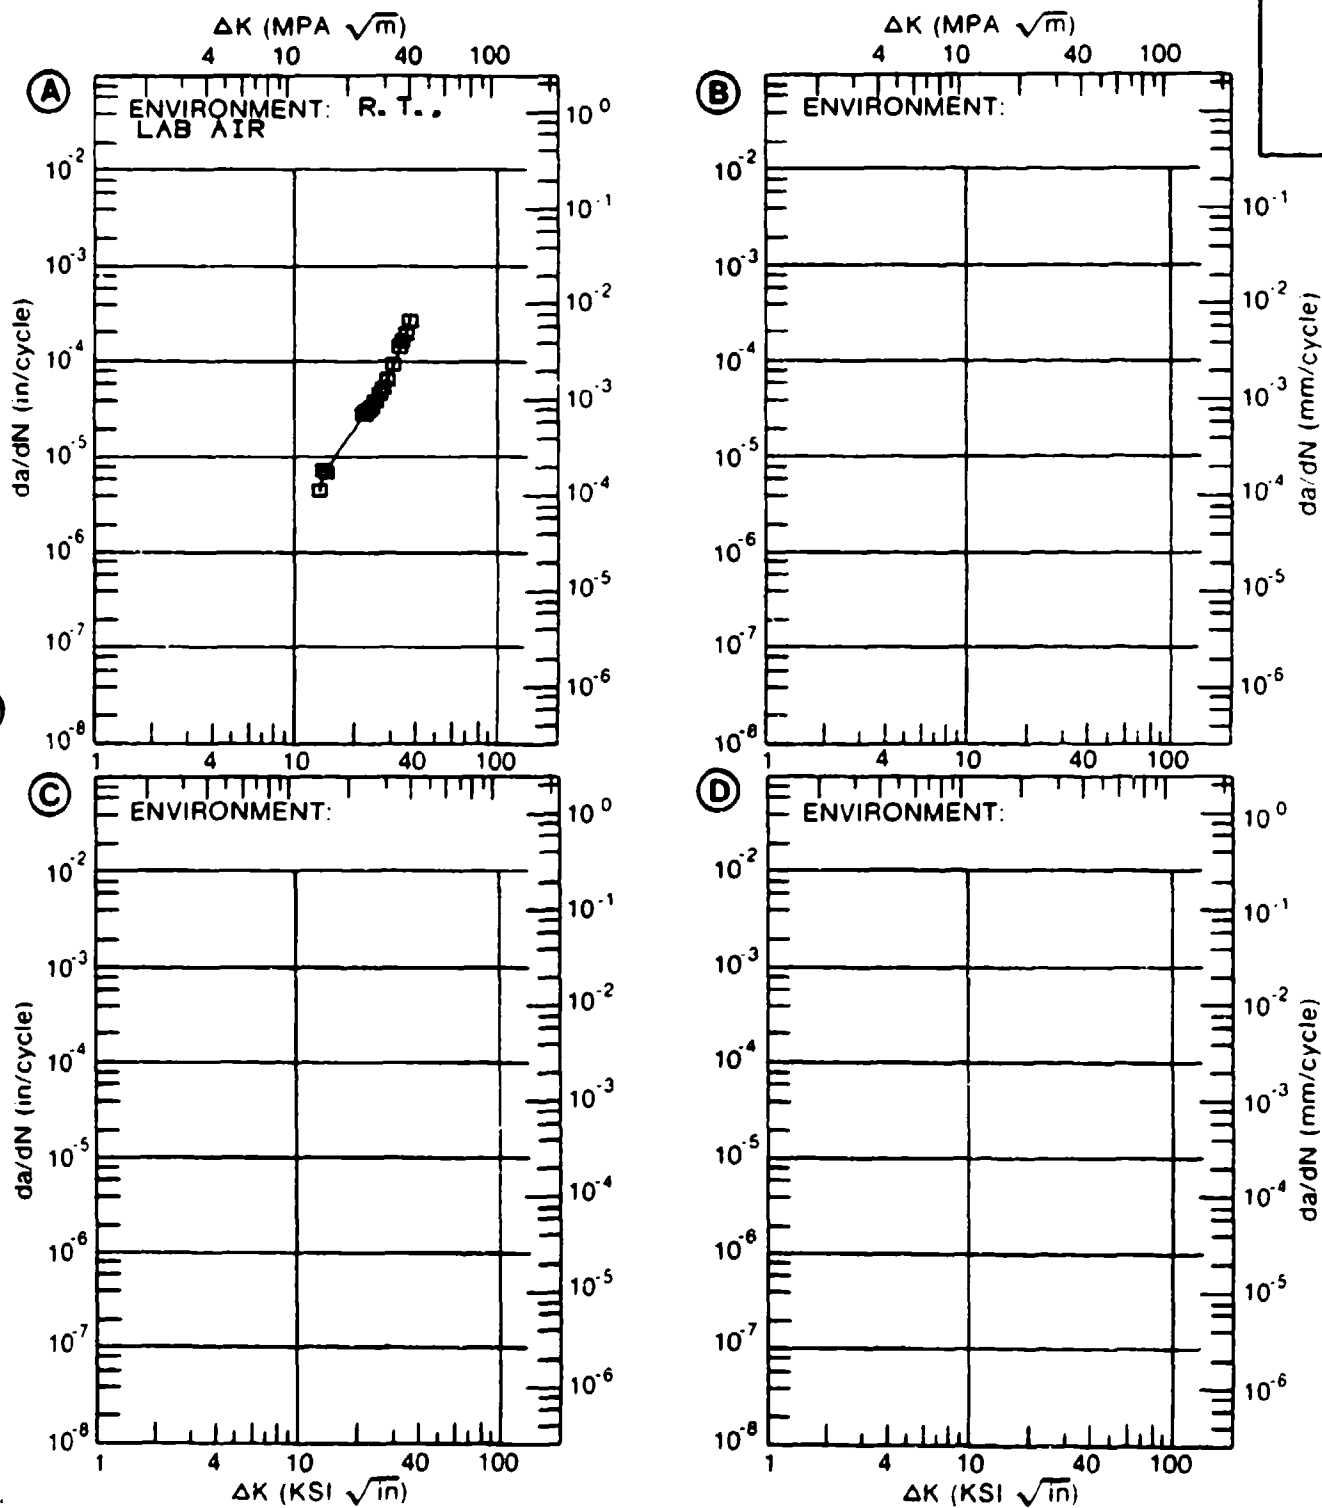


Figure 4.11.3.74

TABLE 4.11.3.75

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.75 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DIST. WATER	E= R. T. 3. 5% NACL	E= R. T. S. T. W.	
DELTA K	A: 9.44	.241			
MIN	B: 8.60		.341		
	C: 9.40			.364	
	D:				
	9.00		.405		
	10.00	.434	.646	.646	
	13.00		2.66		
DELTA K	A: 11.75	1.32			
MAX	B: 13.55		3.37		
	C: 12.61			2.09	
	D:				
ROOT MEAN SQUARE		15.71	16.16	11.43	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.00
 FREQUENCY: 15.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES 00140

TITAN.
 ALLOY
 TI-6AL-
 4V

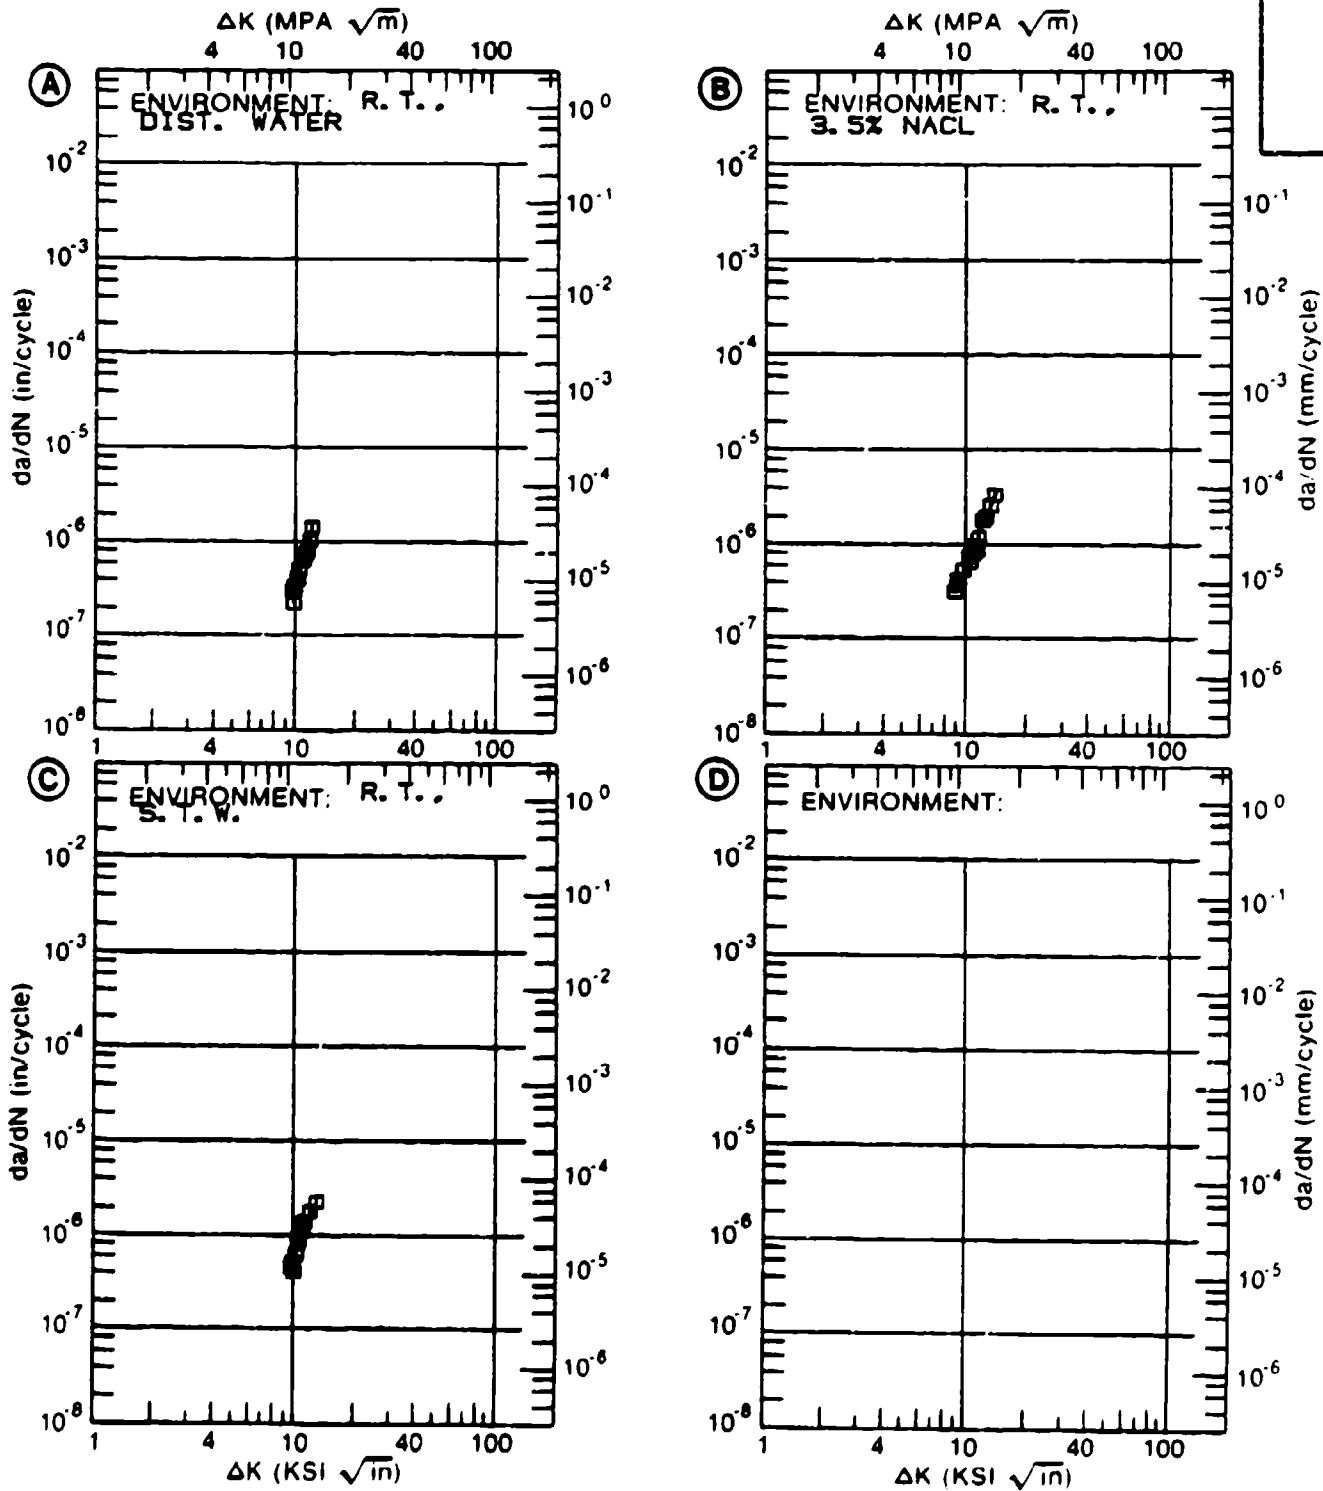


Figure 4.11.3.75

TABLE 4.11.3.76

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.76 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: RA

TI-6AL-4V

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H2O STAURATED JP-4 FUEL	E= R. T. DIST. WATER	
DELTA K	A: 12.23	1.04			
MIN	B: 28.27		32.7		
	C: 26.64			30.5	
	D:				
	13.00	1.45			
	16.00	3.88			
	20.00	9.08			
	25.00	18.5			
	30.00	31.5	36.7	44.5	
	35.00	49.5	51.9	67.7	
	40.00	74.9	75.9	96.3	
	50.00	164.	179.	197.	
	60.00		465.	455.	
	70.00		1304.	1228.	
	80.00			3814.	
DELTA K	A: 58.67	322.			
MAX	B: 71.17		1476.		
	C: 81.31			4465.	
	D:				
ROOT MEAN SQUARE		25.19	10.30	22.32	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 88140

TITAN.
 ALLOY

TI-6AL-
 4V

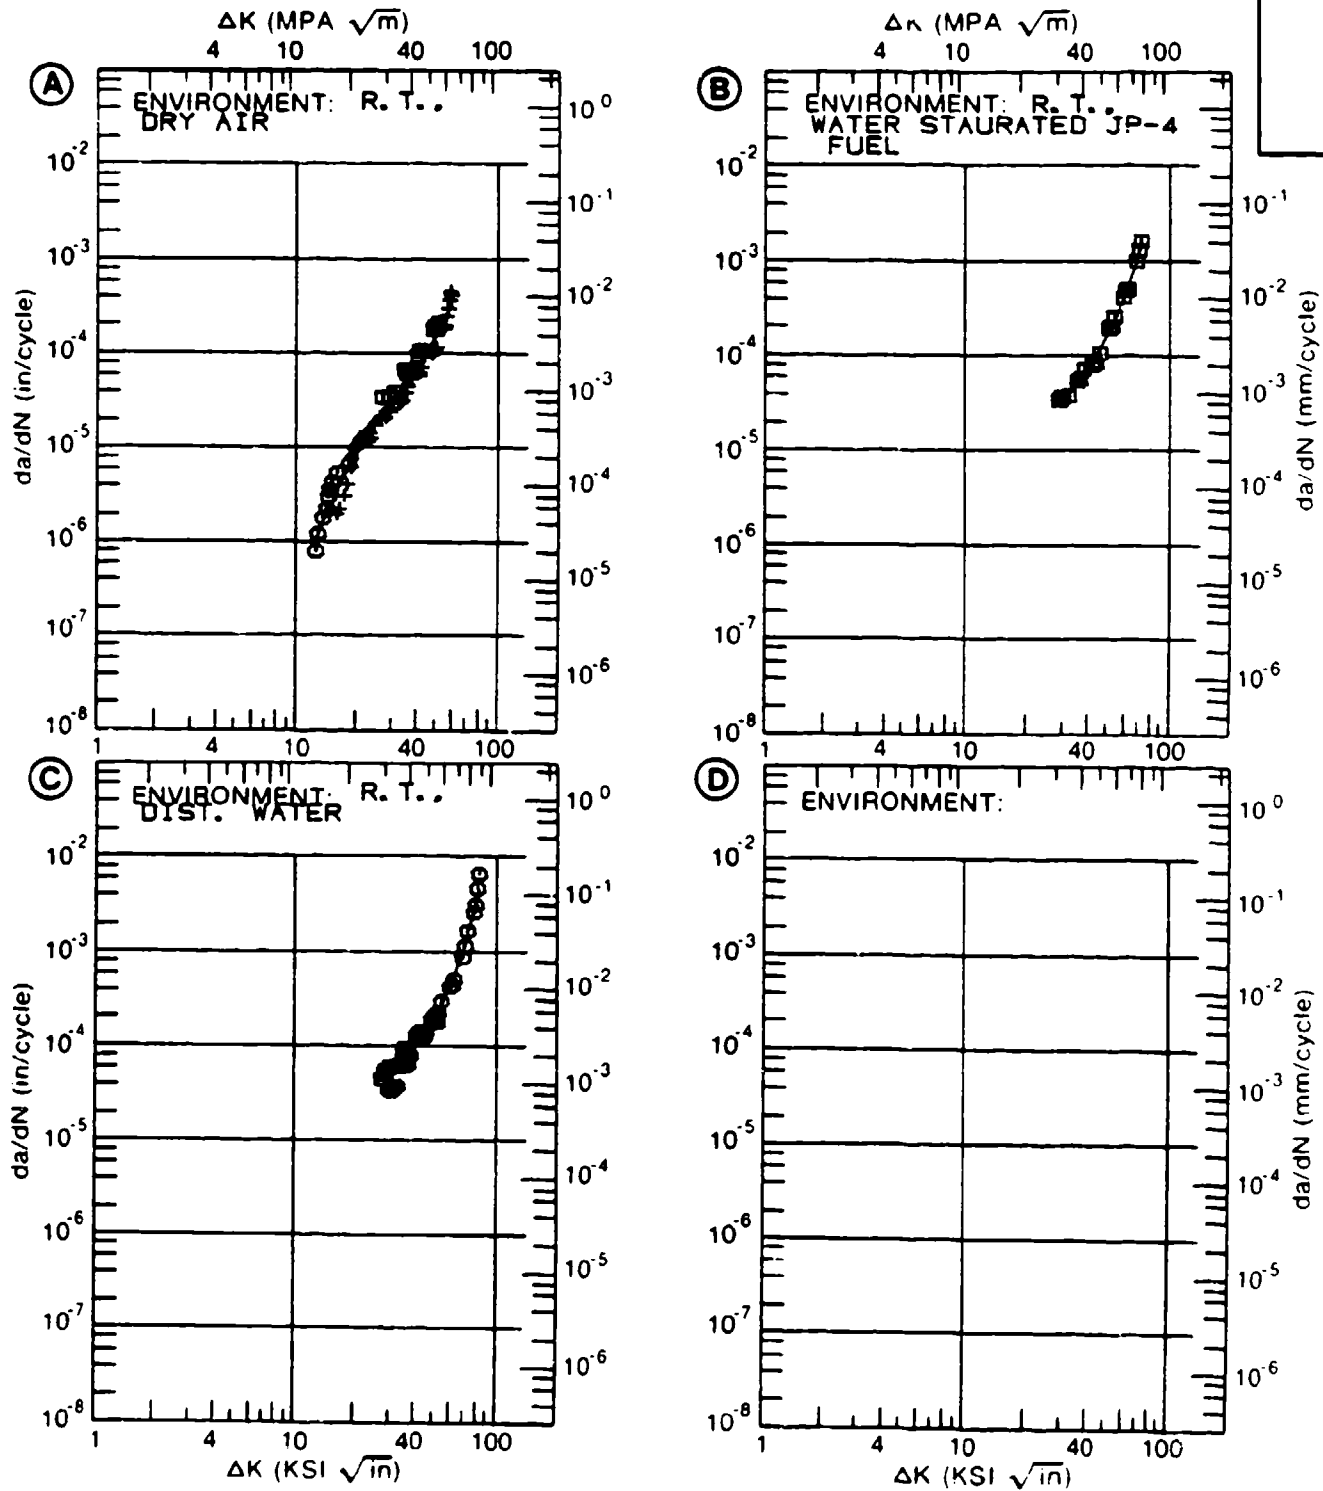


Figure 4.11.3.76

TABLE 4.11.3.77

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.77 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. 3. 5% NA CL	E= R. T. S. T. W.		
DELTA K	A: 14.96	14.1			
MIN	B: 28.42		84.9		
	C:				
	D:				
	16.00	16.3			
	20.00	28.6			
	25.00	54.7			
	30.00	97.2	100.		
	35.00	161.	144.		
	40.00	251.	187.		
	50.00	526.	310.		
	60.00	943.	604.		
	70.00	1504.	1456.		
	80.00		4302.		
DELTA K	A: 72.43	1660.			
MAX	B: 81.35		5050.		
	C:				
	D:				
ROOT MEAN SQUARE		14.68	8.17		
PERCENT ERROR					
LIFE	0 0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 00140

TITAN.
 ALLOY

TI-6AL-4V

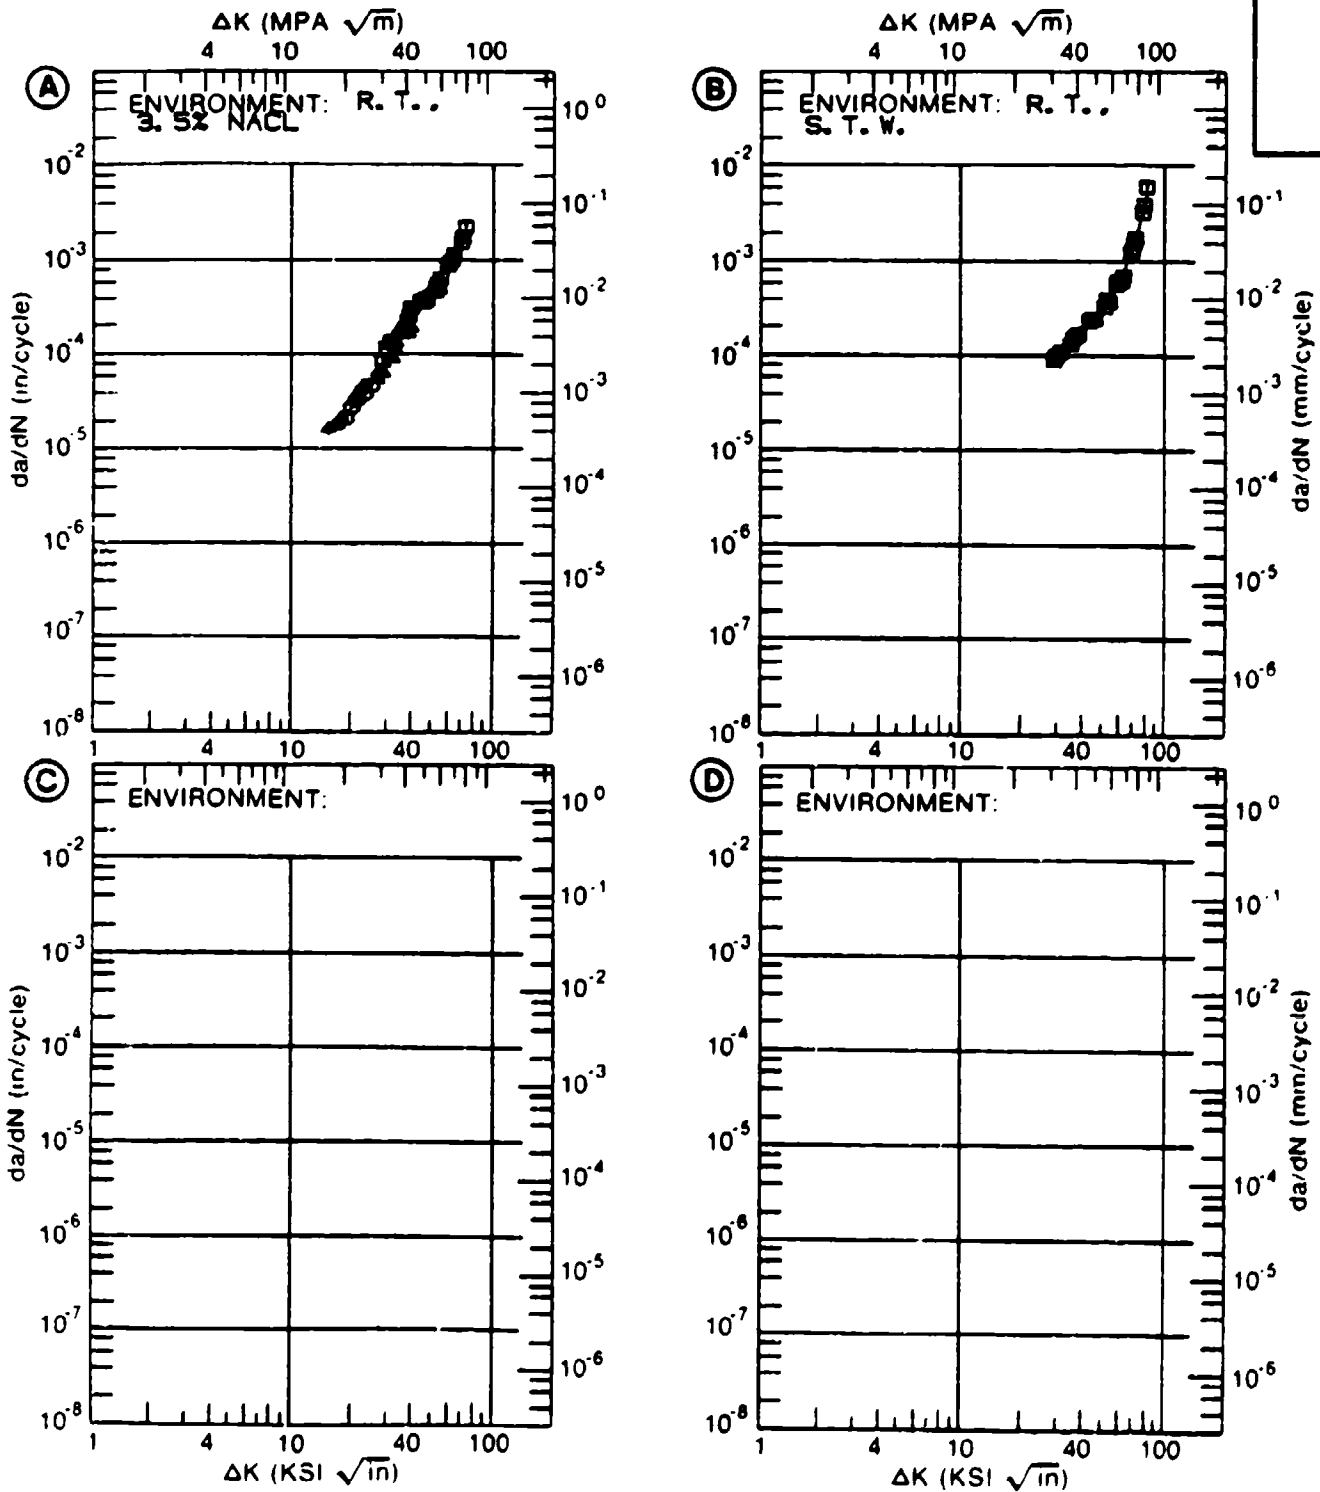


Figure 4.11.3.77

TABLE 4.11.3.78

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.78 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KBI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H2O SATURATED JP-4 FUEL	E= R. T. DIST. WATER	
DELTA K	A: 27.66	26.8			
MIN	B: 28.99		42.8		
	C: 14.90			3.43	
	D:				
	16.00			6.83	
	20.00			19.0	
	25.00			34.4	
	30.00	37.9	47.2	63.3	
	35.00	66.1	70.6	105.	
	40.00	101.	99.2	152.	
	50.00	224.	204.	254.	
	60.00	582.	507.	468.	
	70.00		1547.	1243.	
DELTA K	A: 62.76	787.			
MAX	B: 79.39		5230.		
	C: 78.93			8143.	
	D:				
ROOT MEAN SQUARE		7.58	13.78	16.77	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 0.10 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 00140

TITAN.
 ALLOY
 TI-6AL-4V

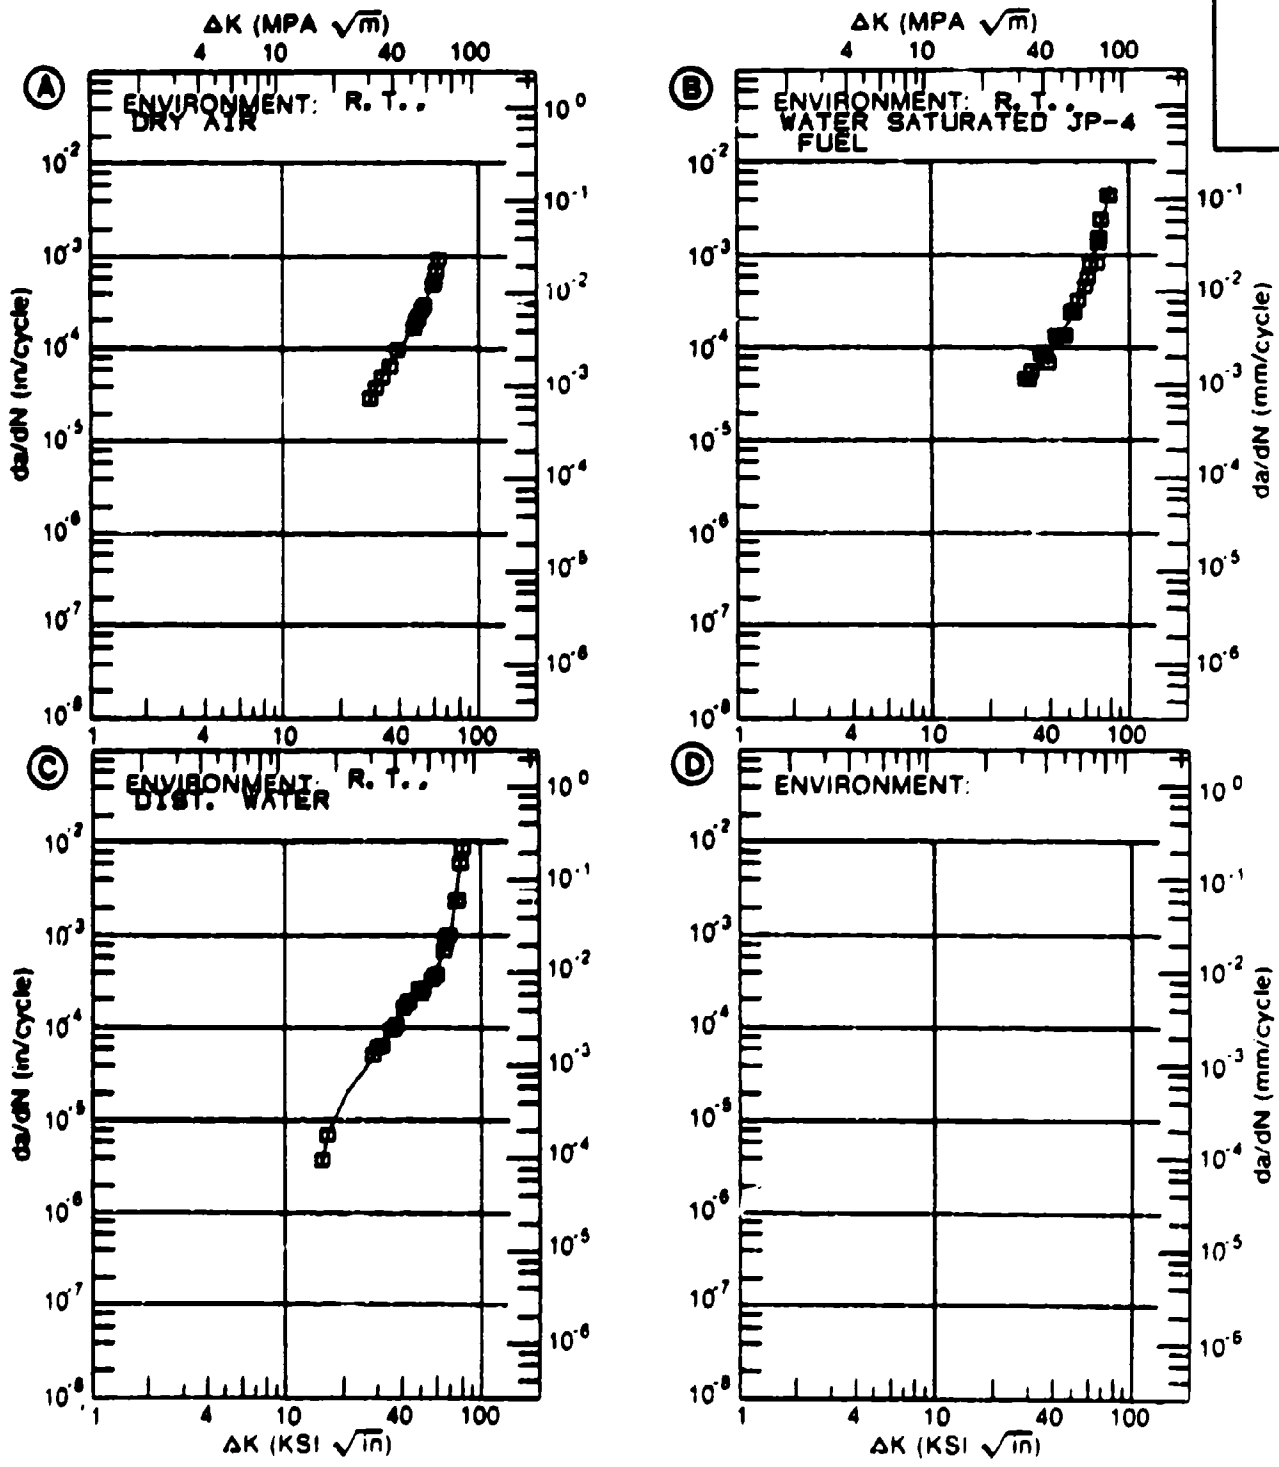


Figure 4.11.3.78

TABLE 4.11.3.79

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.79 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. 3. 5% NACL	E= R. T. S. T. W.		
DELTA K MIN	A: 26. 28	363.			
	B: 30. 23		143.		
	C:				
	D:				
	30. 00	642.			
	35. 00	984.	286.		
	40. 00	1262.	449.		
50. 00	1852.	905.			
60. 00	3042.	2145.			
70. 00	6176.				
DELTA K MAX	A: 75. 42	9991.			
	B: 60. 36		2225.		
	C:				
	D:				
ROOT MEAN SQUARE		18. 75	15. 79		
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25				
SUMMARY	1. 25-2. 0				
(NP/NA)	>2. 0				

CONDITION/HT: RA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 0.10 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 88140

TITAN.
 ALLOY
 TI-8AL-
 4V

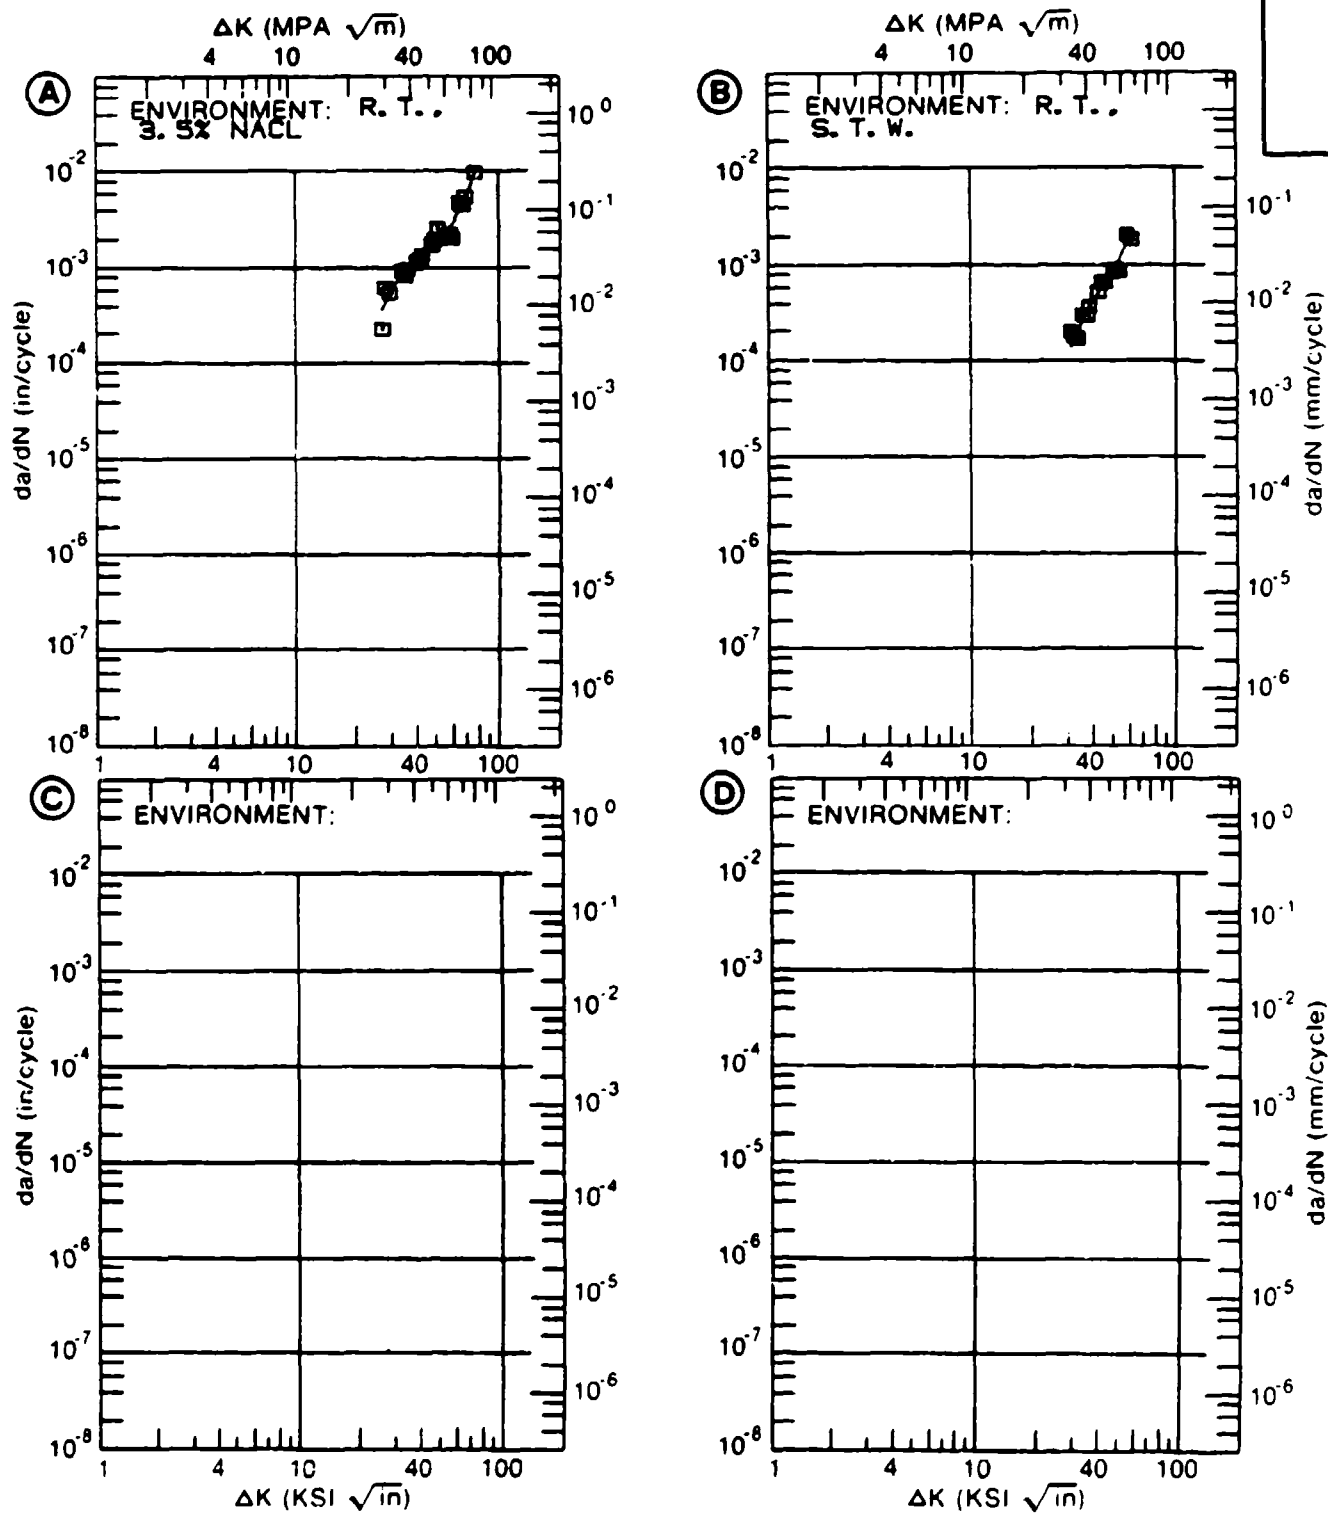


Figure 4.11.3.79

TABLE 4.11.3.80

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.80 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H2O SATURATED JP-4 FUEL	E= R. T. ALT JP-4 FUEL & DIST. WATER	
DELTA K	A: 7.95	.364			
MIN	B: 8.65		.789		
	C: 7.94			1.07	
	D:				
	8.00	.381		1.07	
	9.00	.840	.950	1.16	
	10.00	1.52	1.53	1.55	
	13.00	4.71	4.57	6.24	
	16.00	9.13	9.49	19.1	
	20.00	17.2	18.4	35.4	
	25.00	34.7	35.1	51.4	
	30.00	71.5	64.4	80.0	
	35.00	157.	120.	157.	
	40.00		278.		
DELTA K	A: 37.05	220.			
MAX	B: 45.45		2354.		
	C: 39.99			396.	
	D:				
ROOT MEAN SQUARE		16.89	17.75	23.26	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 88140

TITAN.
 ALLOY

TI-6AL-
 4V

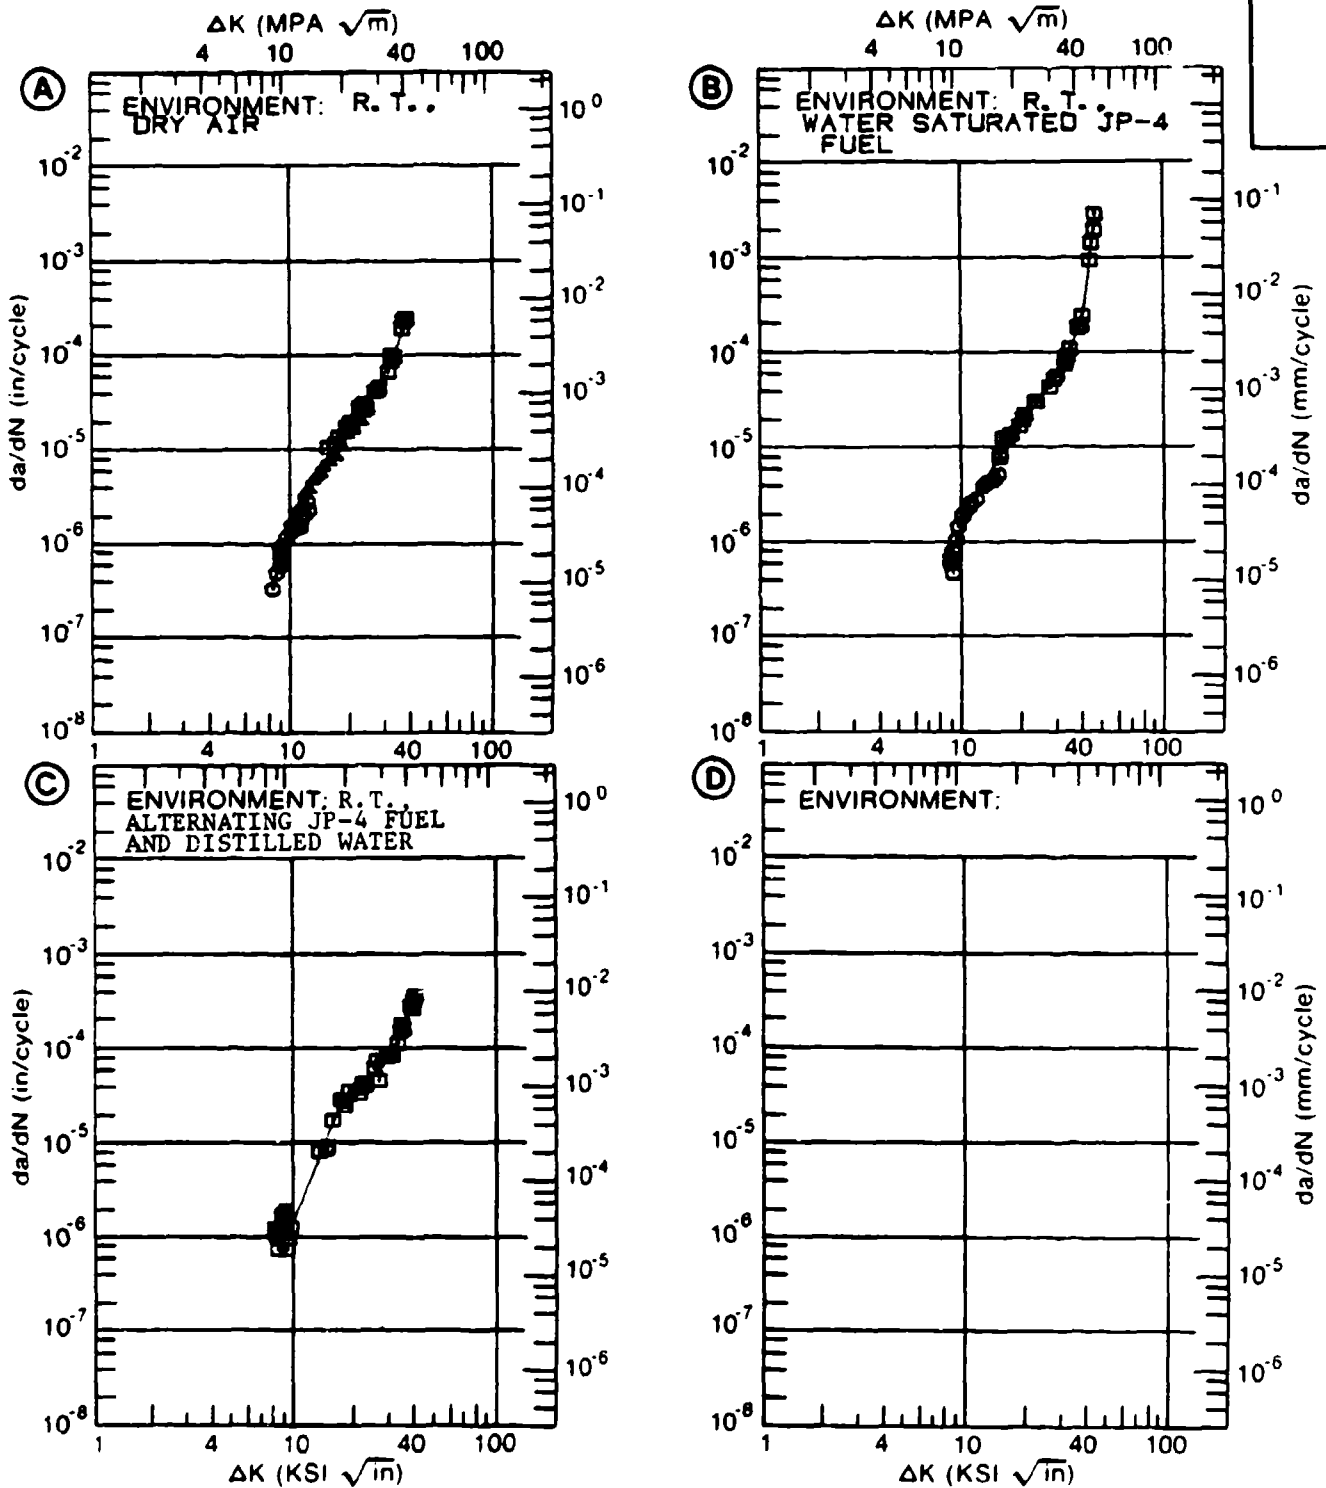


Figure 4.11.3.80

TABLE 4.11.3.81

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.81 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E=+ 175F DRY AIR	E=+ 175F JP-4 FUEL	E=+ 175F DIST. WATER	E=+ 175F 3. 5% NACL
DELTA K	A: 15. 65	6. 24			
MIN	B: 16. 60		10. 4		
	C: 15. 44			13. 0	
	D: 16. 62				39. 9
	16. 00	6. 72		15. 2	
	20. 00	13. 3	16. 9	29. 6	266.
	25. 00	24. 8	27. 0	43. 6	477.
	30. 00	41. 7	40. 7	60. 8	537.
	35. 00	67. 2	64. 2	93. 6	698.
	40. 00	107.	109.	166.	1277.
DELTA K	A: 42. 30	133.			
MAX	B: 45. 72		219.		
	C: 44. 48			314.	
	D: 46. 18				4629.
ROOT MEAN SQUARE		9. 95	6. 80	6. 53	36. 25
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25				
SUMMARY	1. 25-2. 0				
(NP/NA)	>2. 0				

CONDITION/HT: RA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 99140

TITAN.
 ALLOY

TI-6AL-
 4V

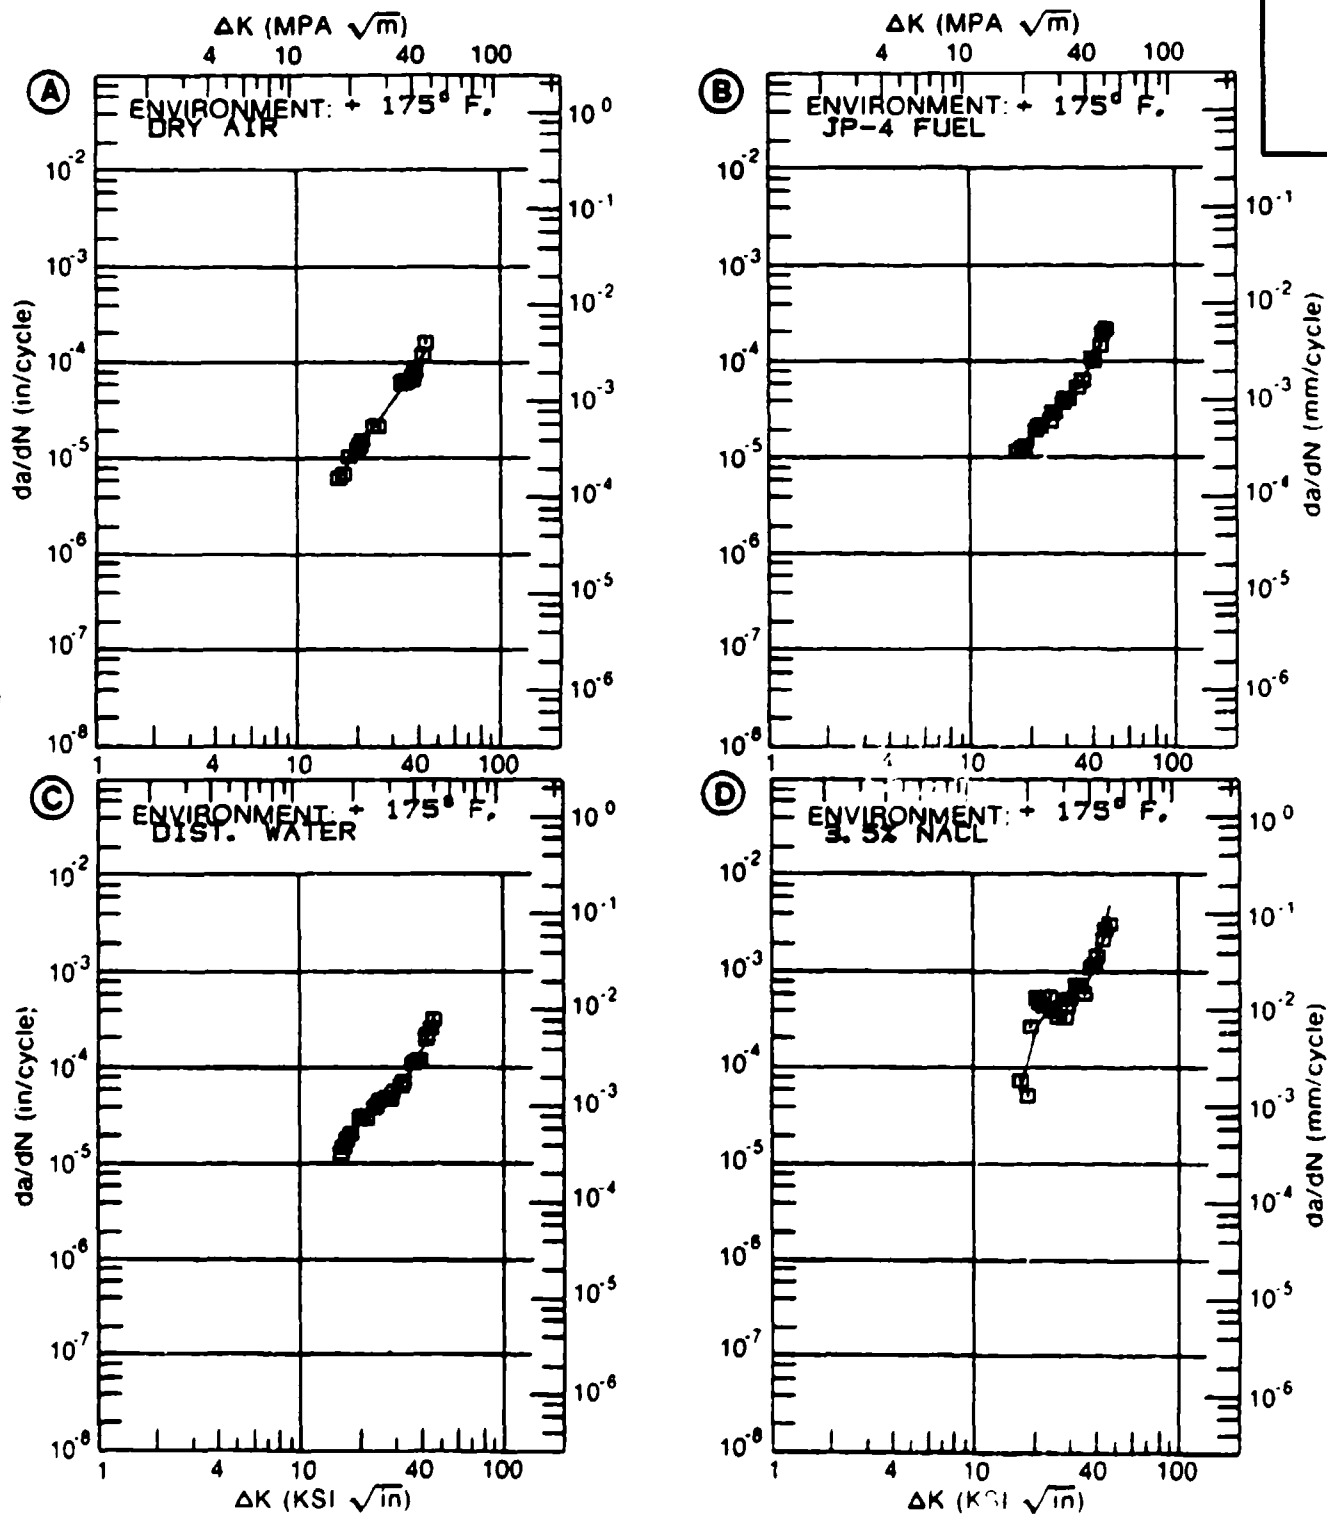


Figure 4.11.3.81

TABLE 4.11.3.82

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.82 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. DIST. WATER	E= R. T. DIST. H2O CRACK SPRAYED WITH LPS-3	E= R. T. 3.5% NaCl	E= R. T. S. T. W.
DELTA K	A: 8.08	.507			
MIN	B: 15.22		11.9		
	C: 8.86			1.02	
	D: 9.27				1.21
	9.00	1.26		1.15	
	10.00	2.64		2.65	2.02
	13.00	10.3		20.3	9.56
	16.00	20.9	11.1	63.4	24.9
	20.00	36.8	22.8	117.	52.5
	25.00	61.9	42.7	165.	93.6
	30.00	102.	65.0	236.	149.
	35.00	177.	121.	401.	235.
	40.00	394.	369.	838.	384.
DELTA K	A: 44.55	1764.			
MAX	B: 44.64		8433.		
	C: 44.53			1937.	
	D: 40.49				403.
ROOT MEAN SQUARE		15.72	32.49	30.11	12.99
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 99140

TITAN.
 ALLOY

TI-6AL-4V

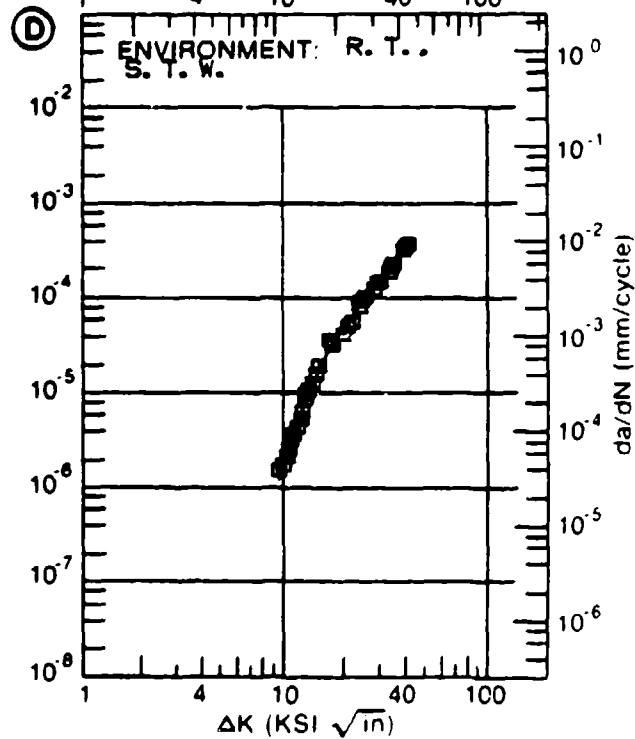
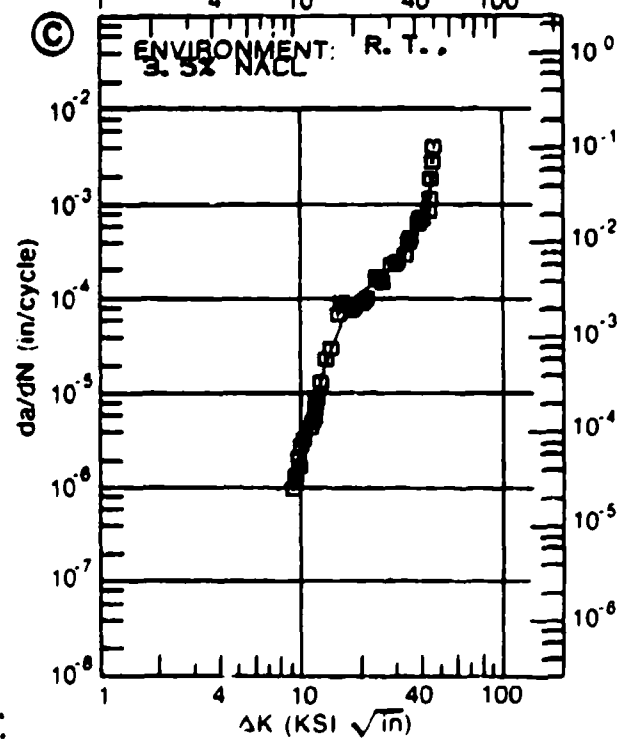
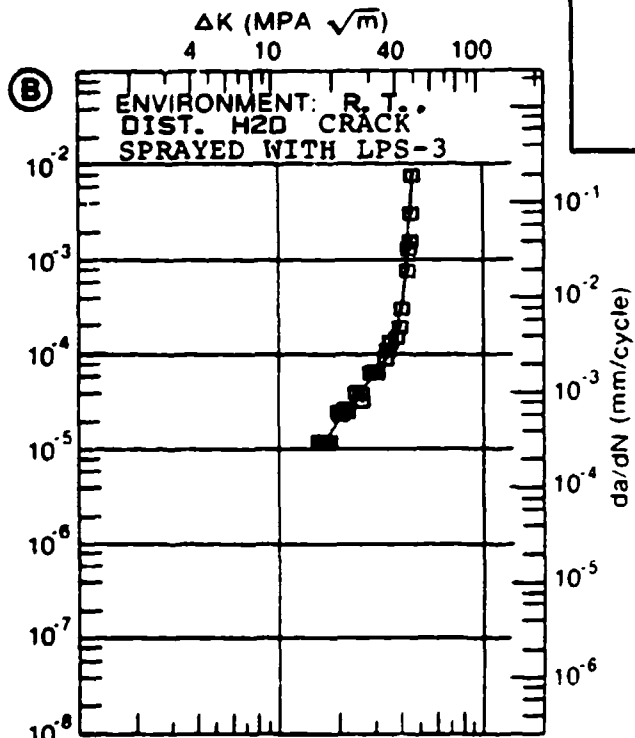
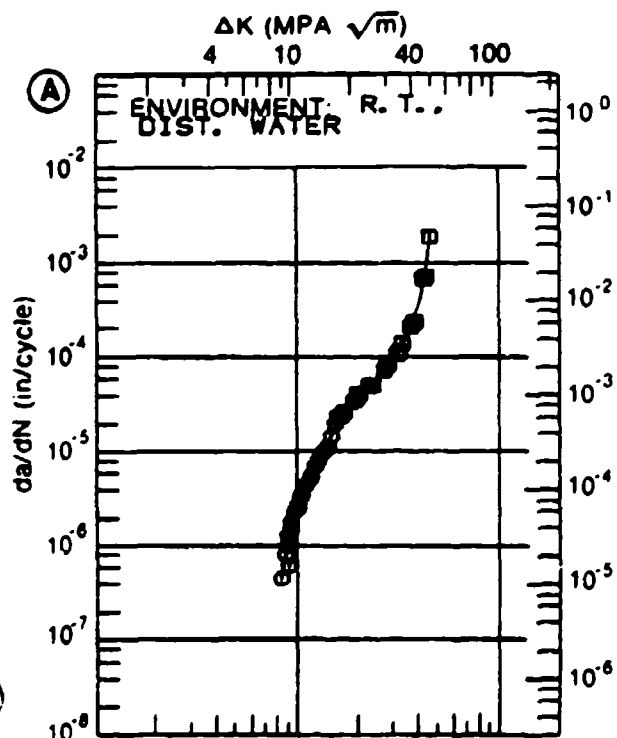


Figure 4.11.3.82

TABLE 4.11.3.83

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.83 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E=- 65F NITROGEN & AIR			
DELTA K	A: 17.05	5.84			
MIN	B:				
	C:				
	D:				
	20.00	12.2			
	25.00	21.7			
	30.00	37.0			
	35.00	83.7			
DELTA K	A: 39.00	209.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		13.05			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 88140

TITAN.
 ALLOY
 TI-6AL-
 4V

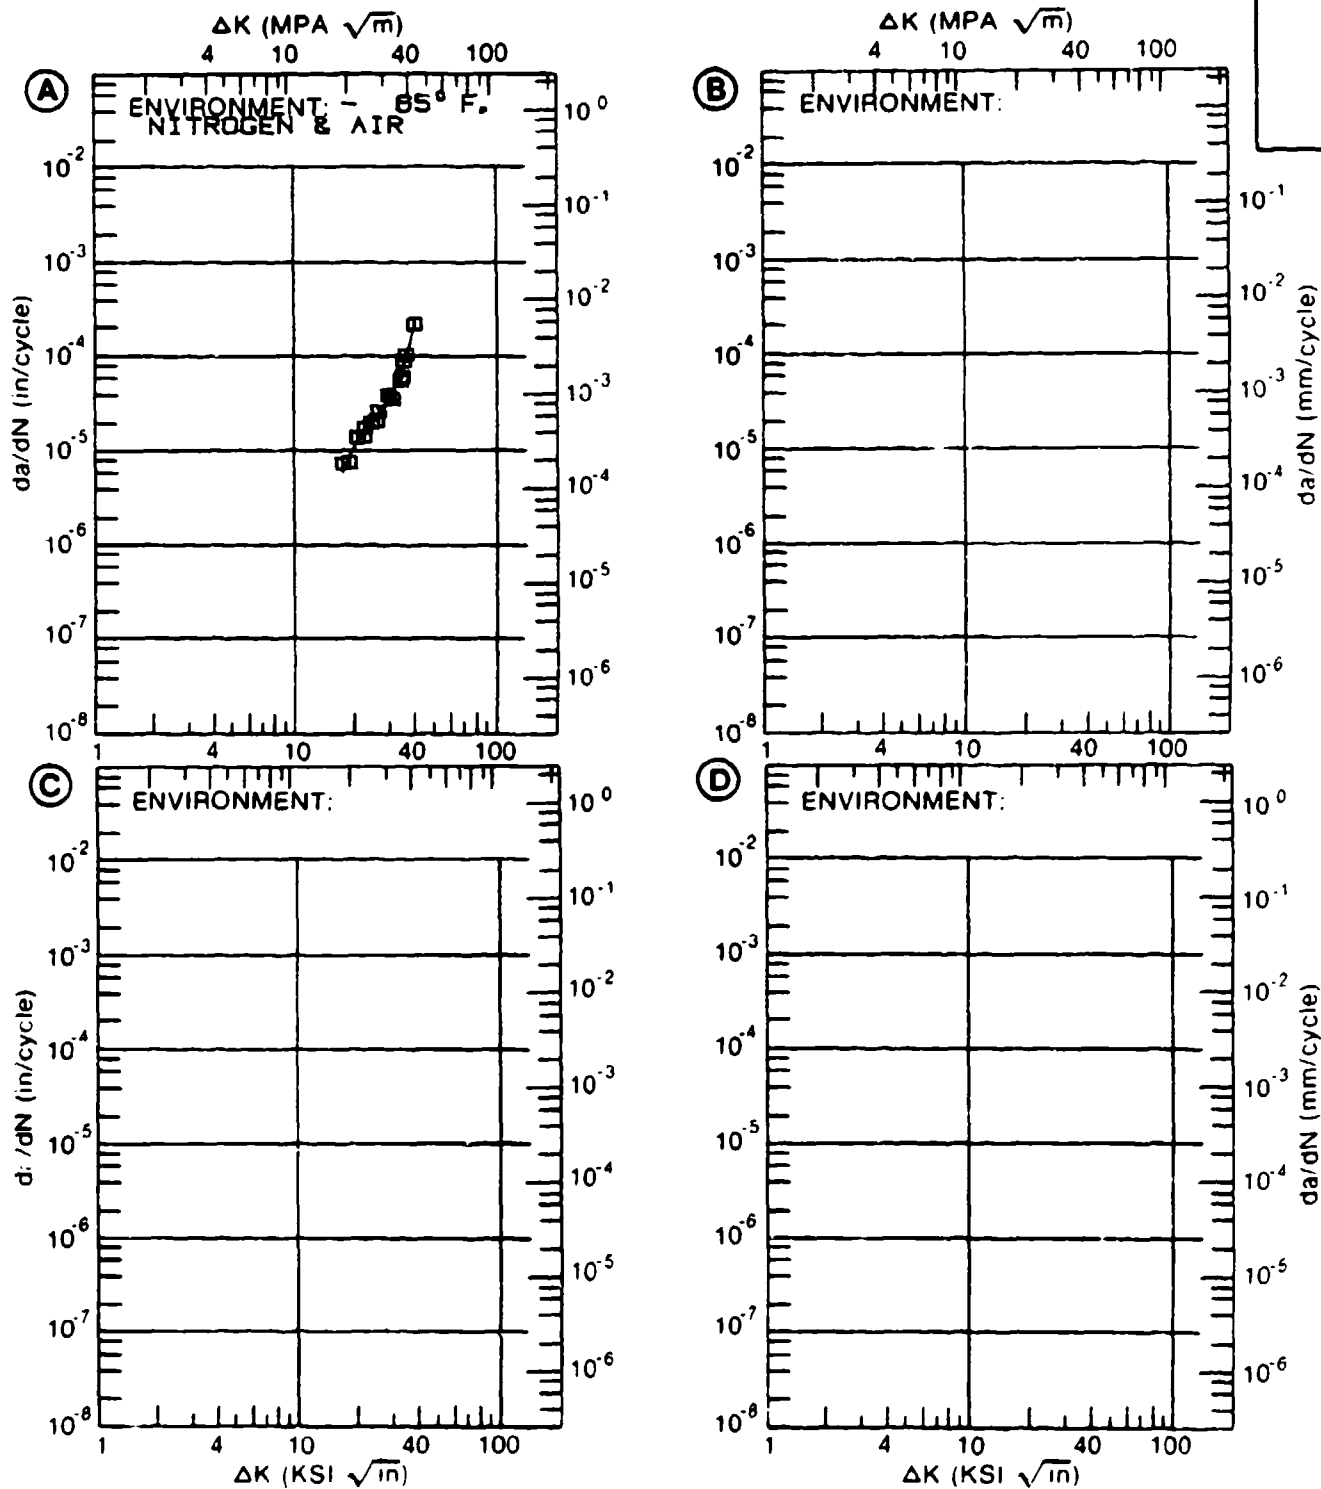


Figure 4.11.3.83

TABLE 4.11.3.84

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.84 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: RA

TI-6AL-4V

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A E= R. T. DRY AIR	B E= R. T. H2O SATURATED JP-4 FUEL	C E= R. T. DIST. WATER	D
A: 8.99	.930			
DELTA K B: 15.67		12.1		
MIN C: 14.81			9.45	
D:				
9.00	.930			
10.00	1.08			
13.00	2.57			
16.00	6.86	12.3	12.2	
20.00	20.4	17.0	21.8	
25.00	48.6	36.3	43.6	
30.00	70.2	70.5	117.	
35.00		128.	391.	
40.00		302.	1251.	
A: 31.84	72.2			
DELTA K B: 46.00		2006.		
MAX C: 40.19			1196.	
D:				
ROOT MEAN SQUARE	92.37	14.73	12.84	
PERCENT ERROR				

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: RA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 0.10 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 99140

TITAN.
 ALLOY
 TI-6AL-
 4V

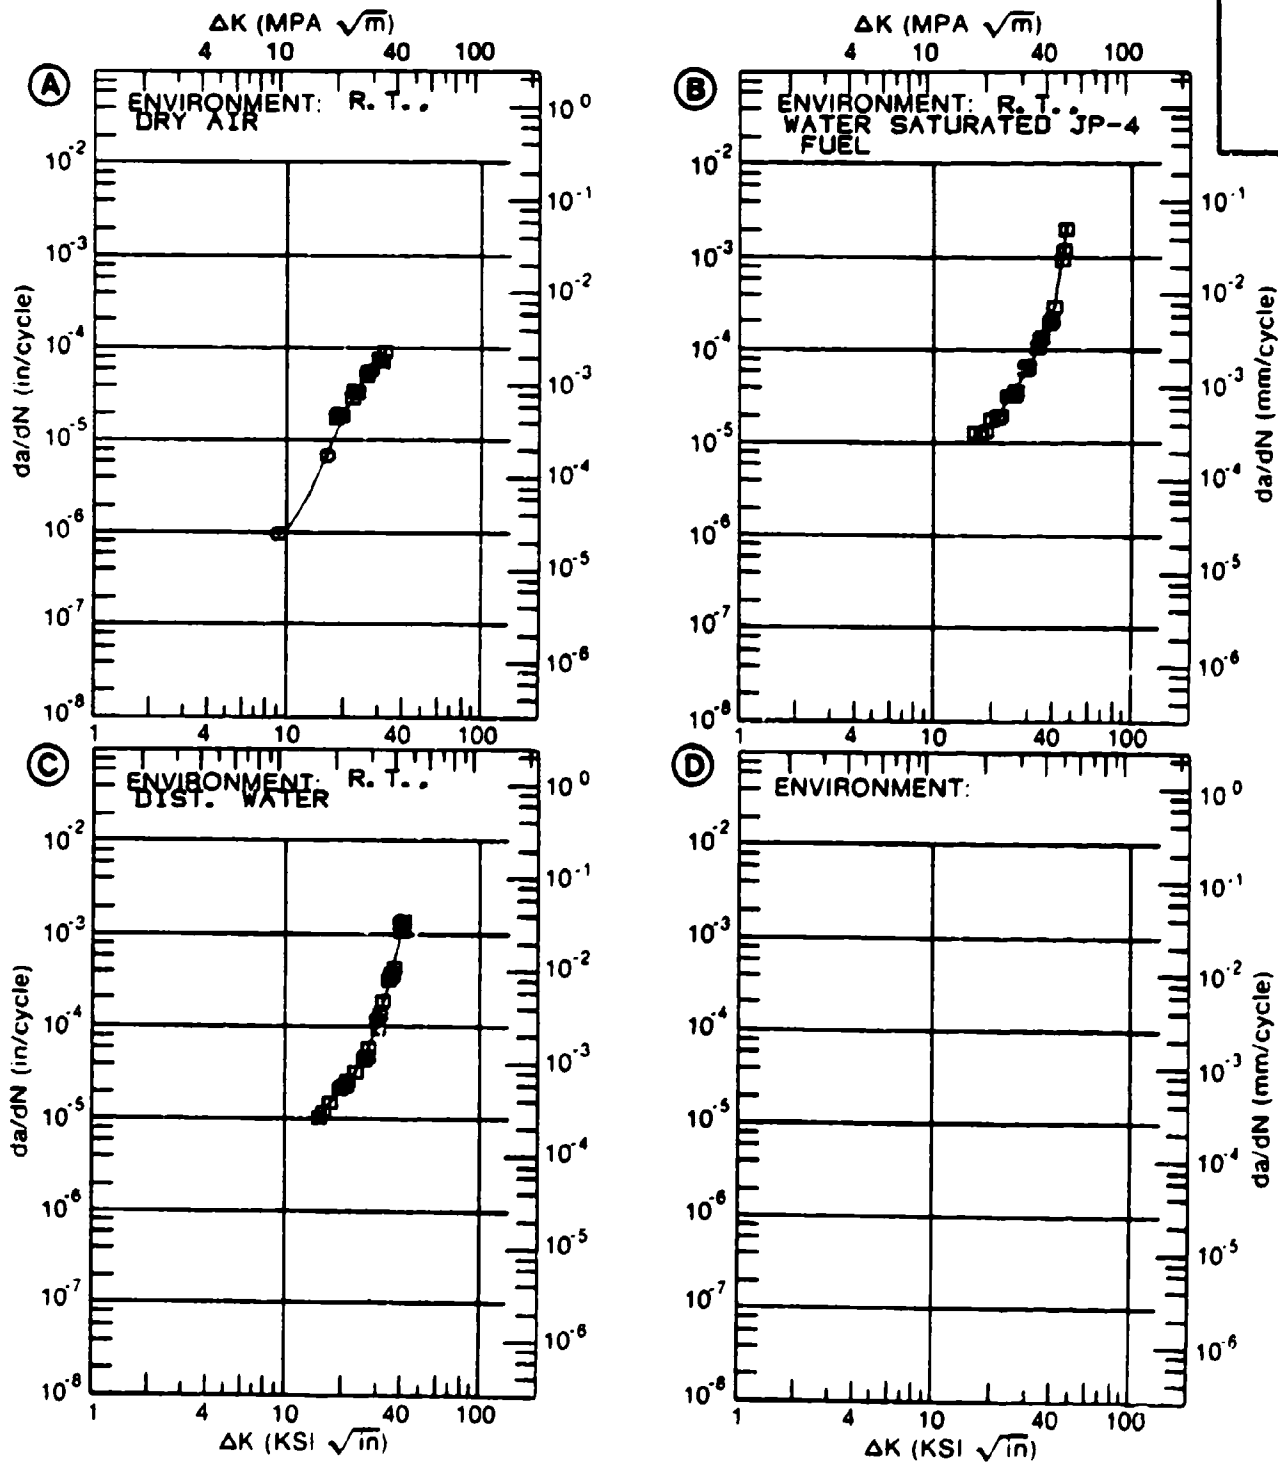


Figure 4.11.3.84

TABLE 4.11.3.85

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.85 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. 3.5% NaCl	E= R. T. S. T. W.		
DELTA K	A: 7.97	.992			
MIN	B: 22.18		77.7		
	C:				
	D:				
	8.00	1.02			
	9.00	1.82			
	10.00	2.55			
	13.00	5.07			
	16.00	14.8			
	20.00				
	25.00		160.		
	30.00		209.		
DELTA K	A: 19.93	31.4			
MAX	B: 34.79		262.		
	C:				
	D:				
ROOT MEAN SQUARE		21.59	10.99		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 0.10 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 00140

TITAN.
 ALLOY

TI-6AL-4V

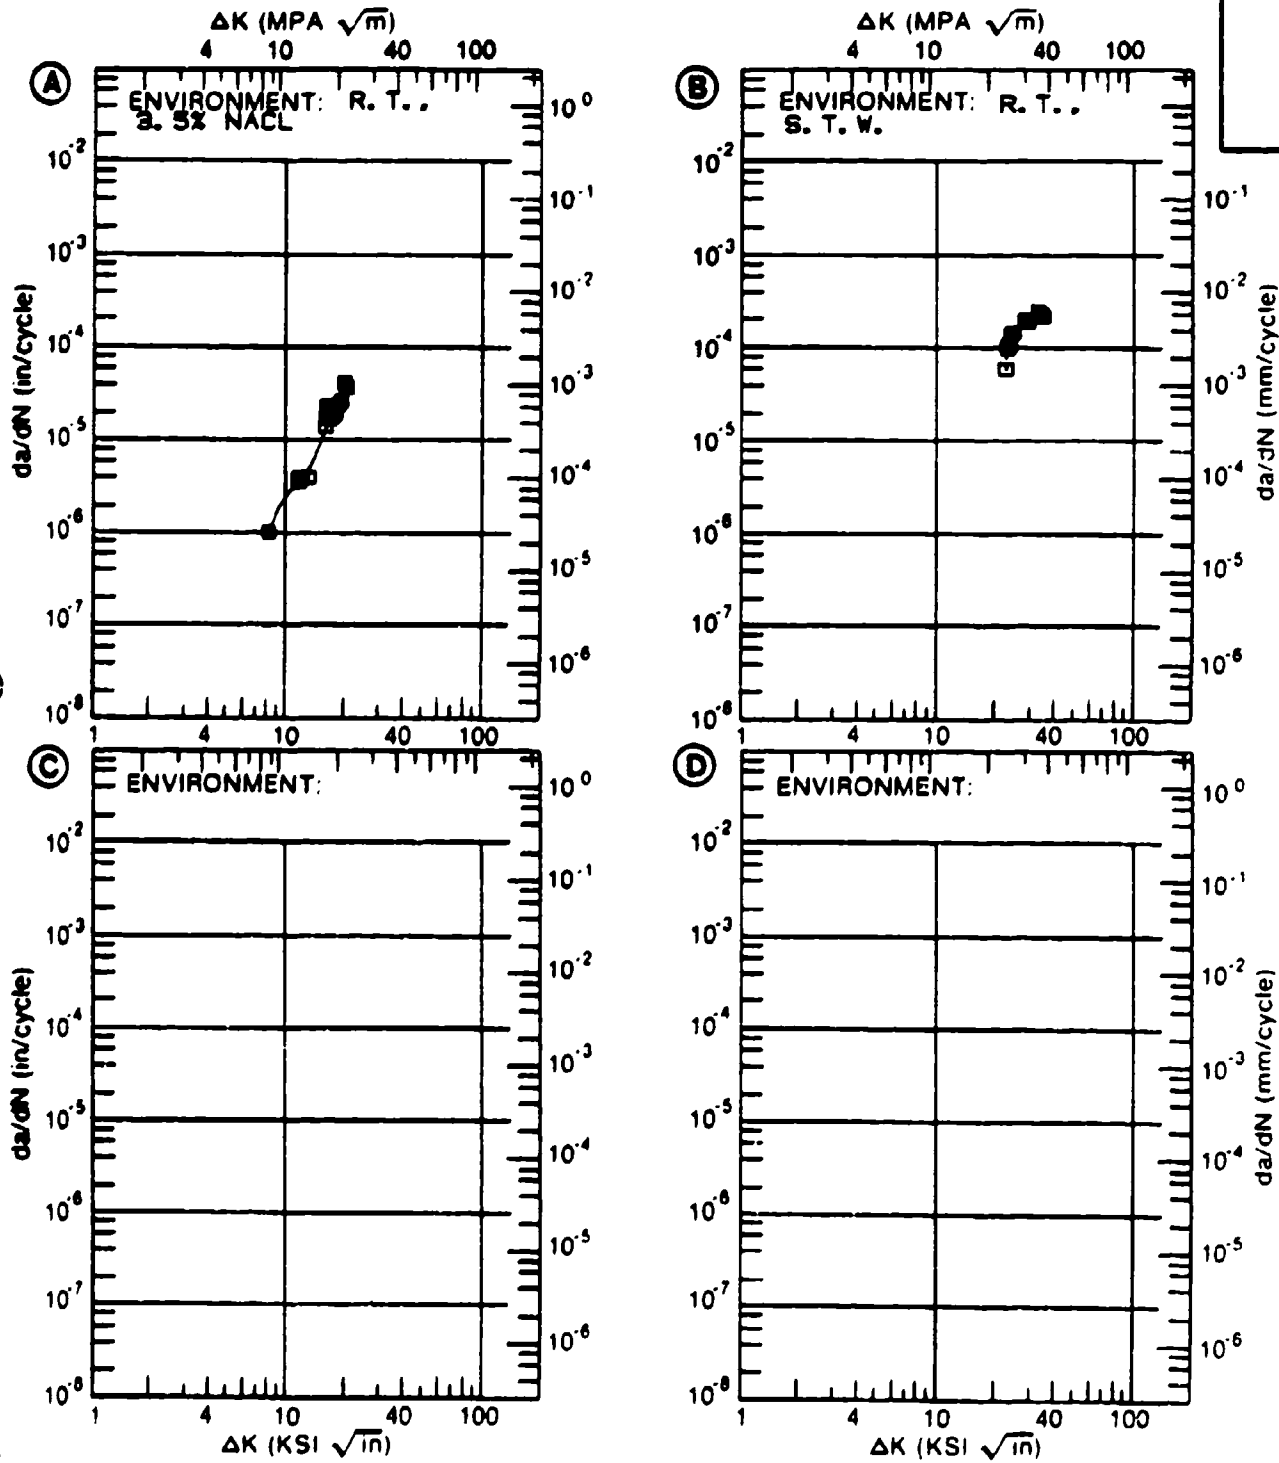


Figure 4.11.3.85

TABLE 4.11.3.86

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.86 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
ENVIRONMENT: R. T. , L. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30	R=+0.50	R=+0.70
	A: 5.98 :	.0135			
DELTA K	B: 6.12 :		.109		
MIN	C: 6.39 :			.226	
	D: 5.11 :				.146
	6.00 :	.0139			.375
	7.00 :	.0485	.229	.371	.798
	8.00 :	.127	.464	.726	1.40
	9.00 :	.270	.839	1.25	2.17
	10.00 :	.499	1.39	1.94	3.12
	13.00 :	1.84	4.24	5.08	7.33
	16.00 :	4.30	8.75	9.54	14.9
	20.00 :	9.42	15.9	16.8	
	25.00 :	19.0	23.2		
	30.00 :	32.7			
	35.00 :	52.2			
	40.00 :	79.4			
	50.00 :	171.			
DELTA K	A: 52.96 :	213.			
MAX	B: 25.92 :		24.1		
	C: 20.65 :			18.1	
	D: 19.21 :				30.8
ROOT MEAN SQUARE		33.97	20.34	21.38	6.79
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8		1	1	
RATIO	0.8-1.25	2	1	1	1
SUMMARY	1.25-2.0	3			
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 113.0- 121.0 KSI
 ULT. STRENGTH: 127.0- 135.0 KSI
 SPECIMEN THK: 0.990- 1.000"
 SPECIMEN WIDTH: 7.400- 7.410"
 REFERENCES: 8579, 85837

TITAN.
 ALLOY
 TI-6AL-
 4V

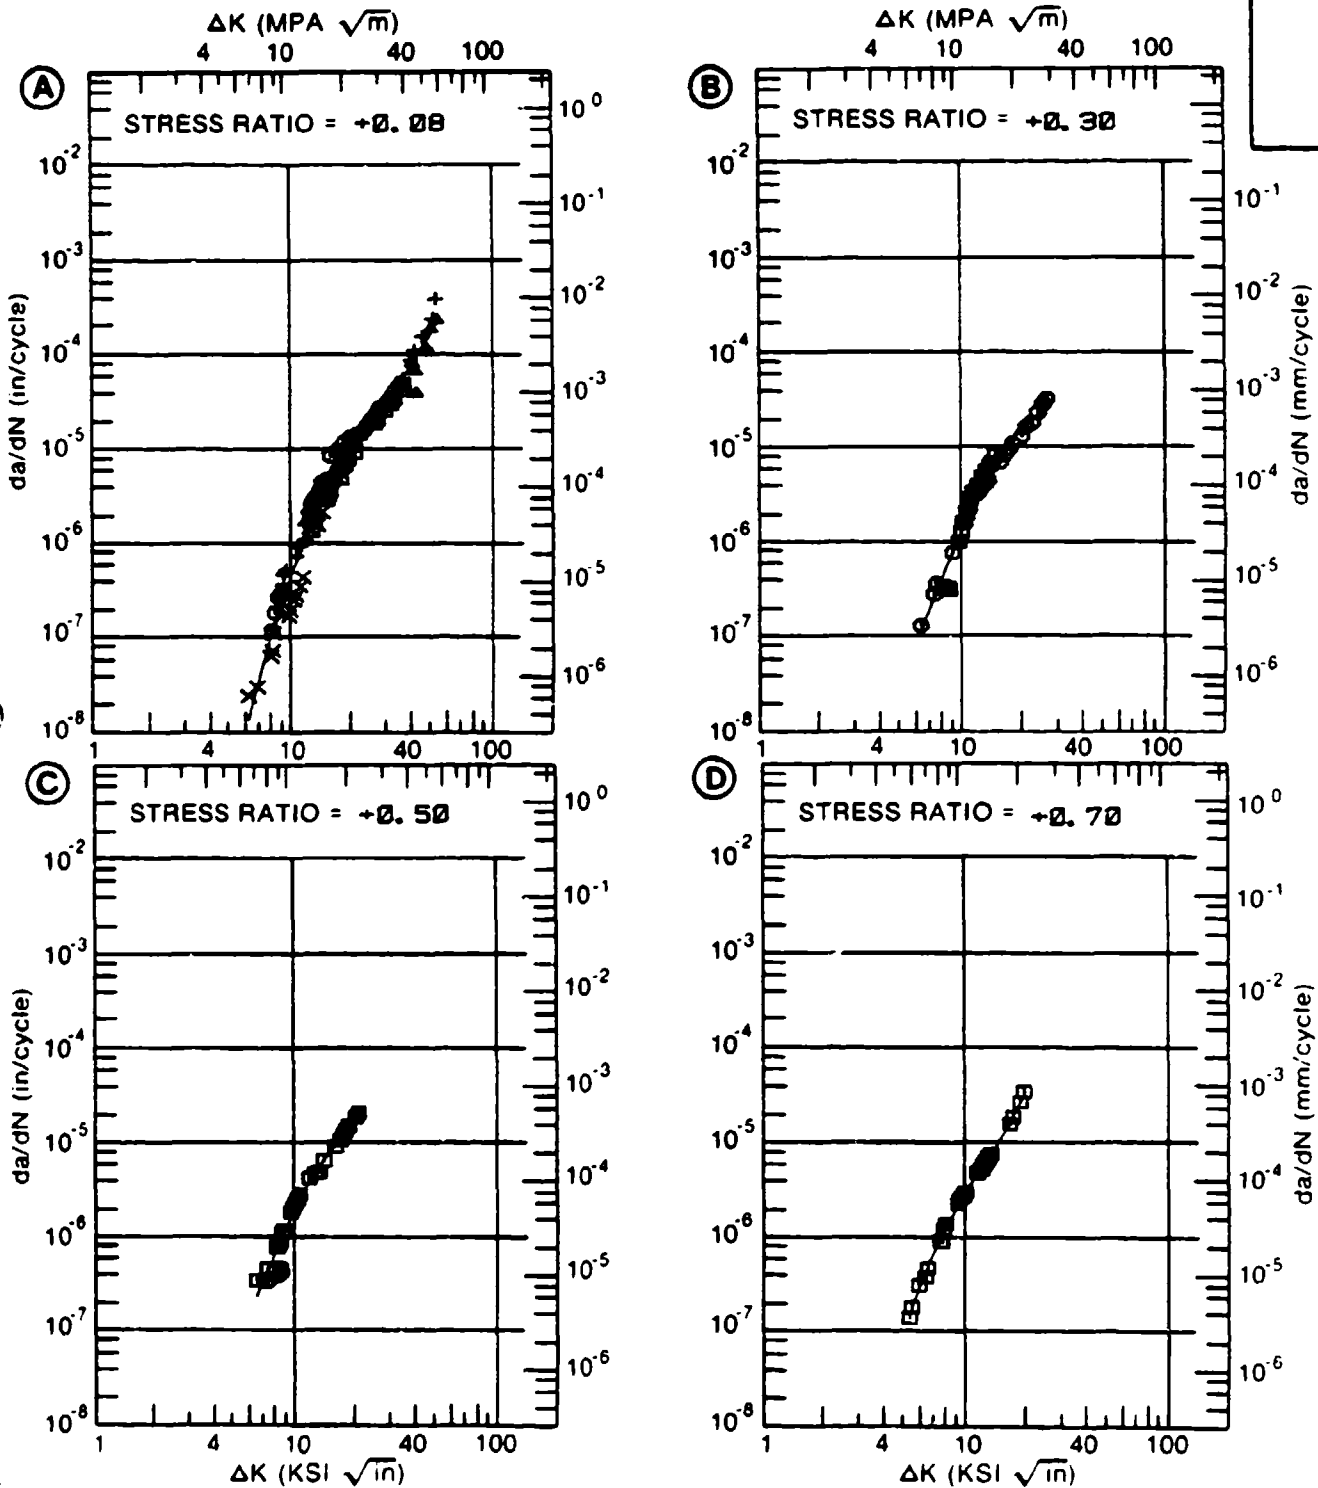


Figure 4.11.3.86

TABLE 4.11.3.87

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.87 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
ENVIRONMENT: R. T. , S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30	R=+0.50	
DELTA K	A: 8.35	.340			
MIN	B: 7.37		.385		
	C: 5.97			.293	
	D:				
	6.00			.300	
	7.00			.649	
	8.00		.784	1.32	
	9.00	.423	1.37	2.46	
	10.00	.590	2.27	4.23	
	13.00	1.52	7.32	13.5	
	16.00	3.49	19.3	24.6	
	20.00	8.98	24.5		
	25.00	23.4			
	30.00	50.6			
	35.00	94.6			
	40.00	158.			
	50.00	344.			
	60.00	591.			
DELTA K	A: 66.77	772.			
MAX	B: 22.54		26.4		
	C: 17.45			28.0	
	D:				
ROOT MEAN SQUARE		58.58	11.40	10.86	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	2			
RATIO	0.8-1.25		1	1	
SUMMARY	1.25-2.0	2			
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 118.0 - 124.0 KSI
 ULT. STRENGTH: 129.0 - 138.0 KSI
 SPECIMEN THK: 0.998 - 0.998"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837, 88579

TITAN.
 ALLOY
 TI-6AL-
 4V

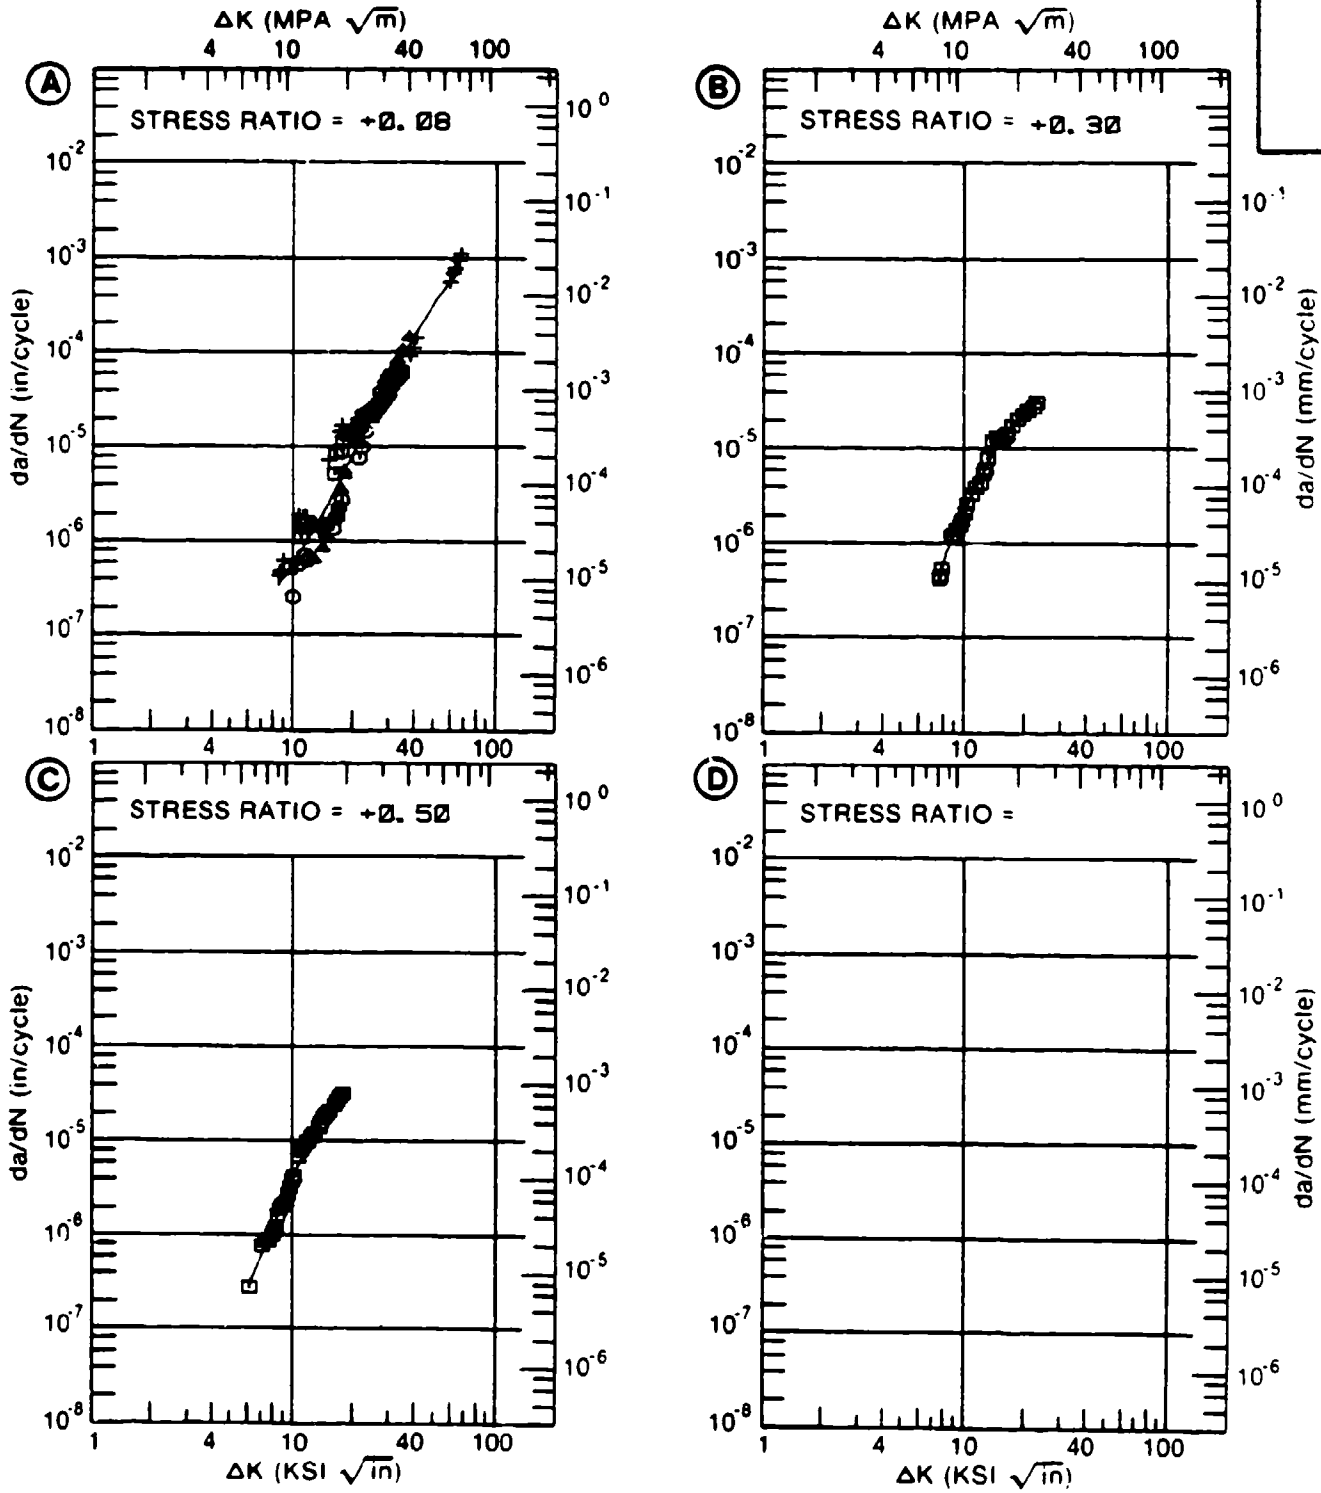


Figure 4.11.3.87

TABLE 4.11.3.88

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.88 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: RA

TI-6AL-4V

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= 65F		E= R. T.	
		L. H. A.		L. H. A.	
DELTA K	A: 12.57	2.09			
MIN	B: 5.98		.0135		
	C:				
	D:				
	6.00		.0139		
	7.00		.0485		
	8.00		.127		
	9.00		.270		
	10.00		.499		
	13.00	2.46	1.84		
	16.00	5.61	4.30		
	20.00	11.1	9.42		
	25.00	20.6	19.0		
	30.00	36.8	32.7		
	35.00		52.2		
	40.00		79.4		
	50.00		171.		
DELTA K	A: 31.93	46.2			
MAX	B: 52.96		213.		
	C:				
	D:				

ROOT MEAN SQUARE
PERCENT ERROR

4.90

33.97

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

1

2

3

CONDITION/HT: RA
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 113.0- 121.0 KSI
 ULT. STRENGTH: 127.0- 135.0 KSI
 SPECIMEN THK: 0.990- 1.000"
 SPECIMEN WIDTH: 7.400- 7.410"
 REFERENCES: 85837, 88579

TITAN.
 ALLOY

TI-6AL-
 4V

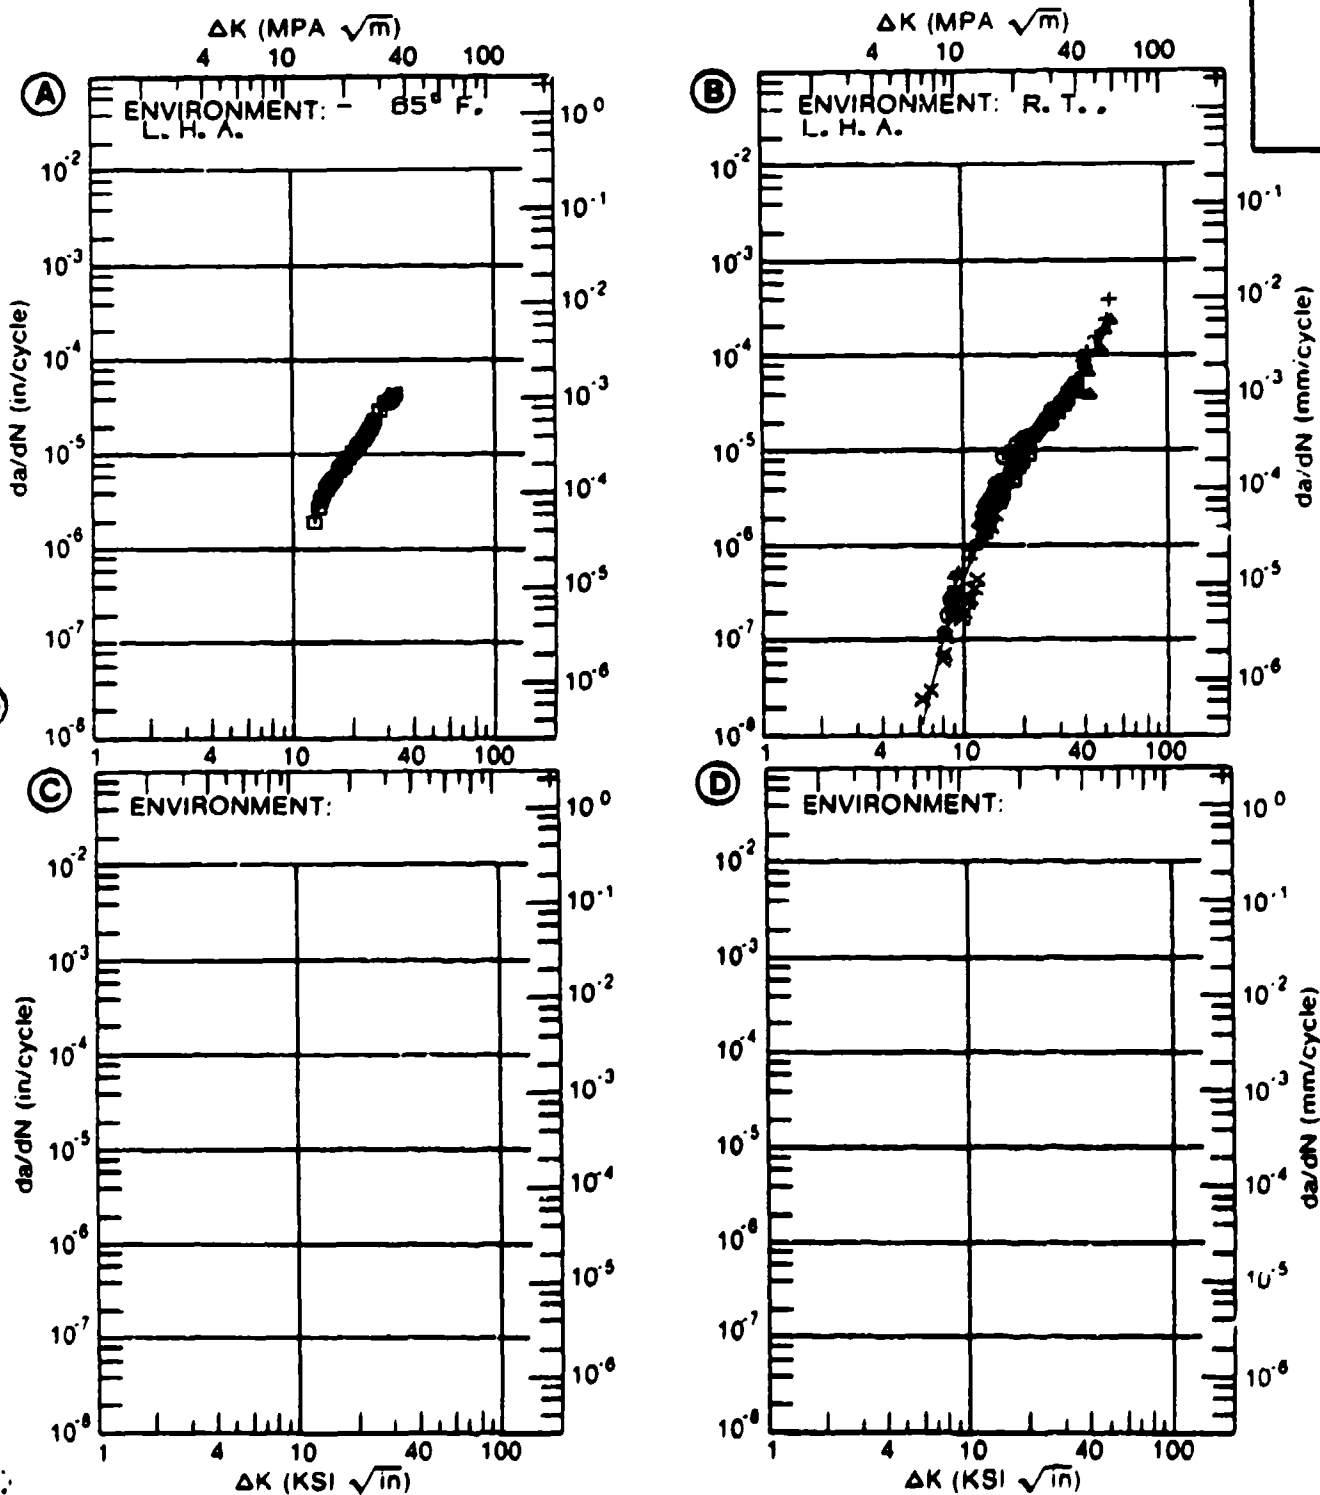


Figure 4.11.3.88

TABLE 4.11.3.89

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.89 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E=+ 265F L. H. A.		
DELTA K	A: 8.22	.230			
MIN	B: 14.47		3.05		
	C:				
	D:				
	9.00	.401			
	10.00	.728			
	13.00	2.59			
	16.00	5.76	5.05		
	20.00	11.3	11.6		
	25.00	18.6	21.8		
	30.00		36.8		
DELTA K	A: 28.48	23.2			
MAX	B: 32.07		45.8		
	C:				
	D:				
ROOT MEAN SQUARE		13.20	8.62		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 118.0- 121.0 KSI
 ULT. STRENGTH: 129.0- 134.0 KSI
 SPECIMEN THK: 0.254- 0.990"
 SPECIMEN WIDTH: 5.000- 7.400"
 REFERENCES: 85837, 88579

TITAN.
 ALLOY
 TI-6AL-
 4V

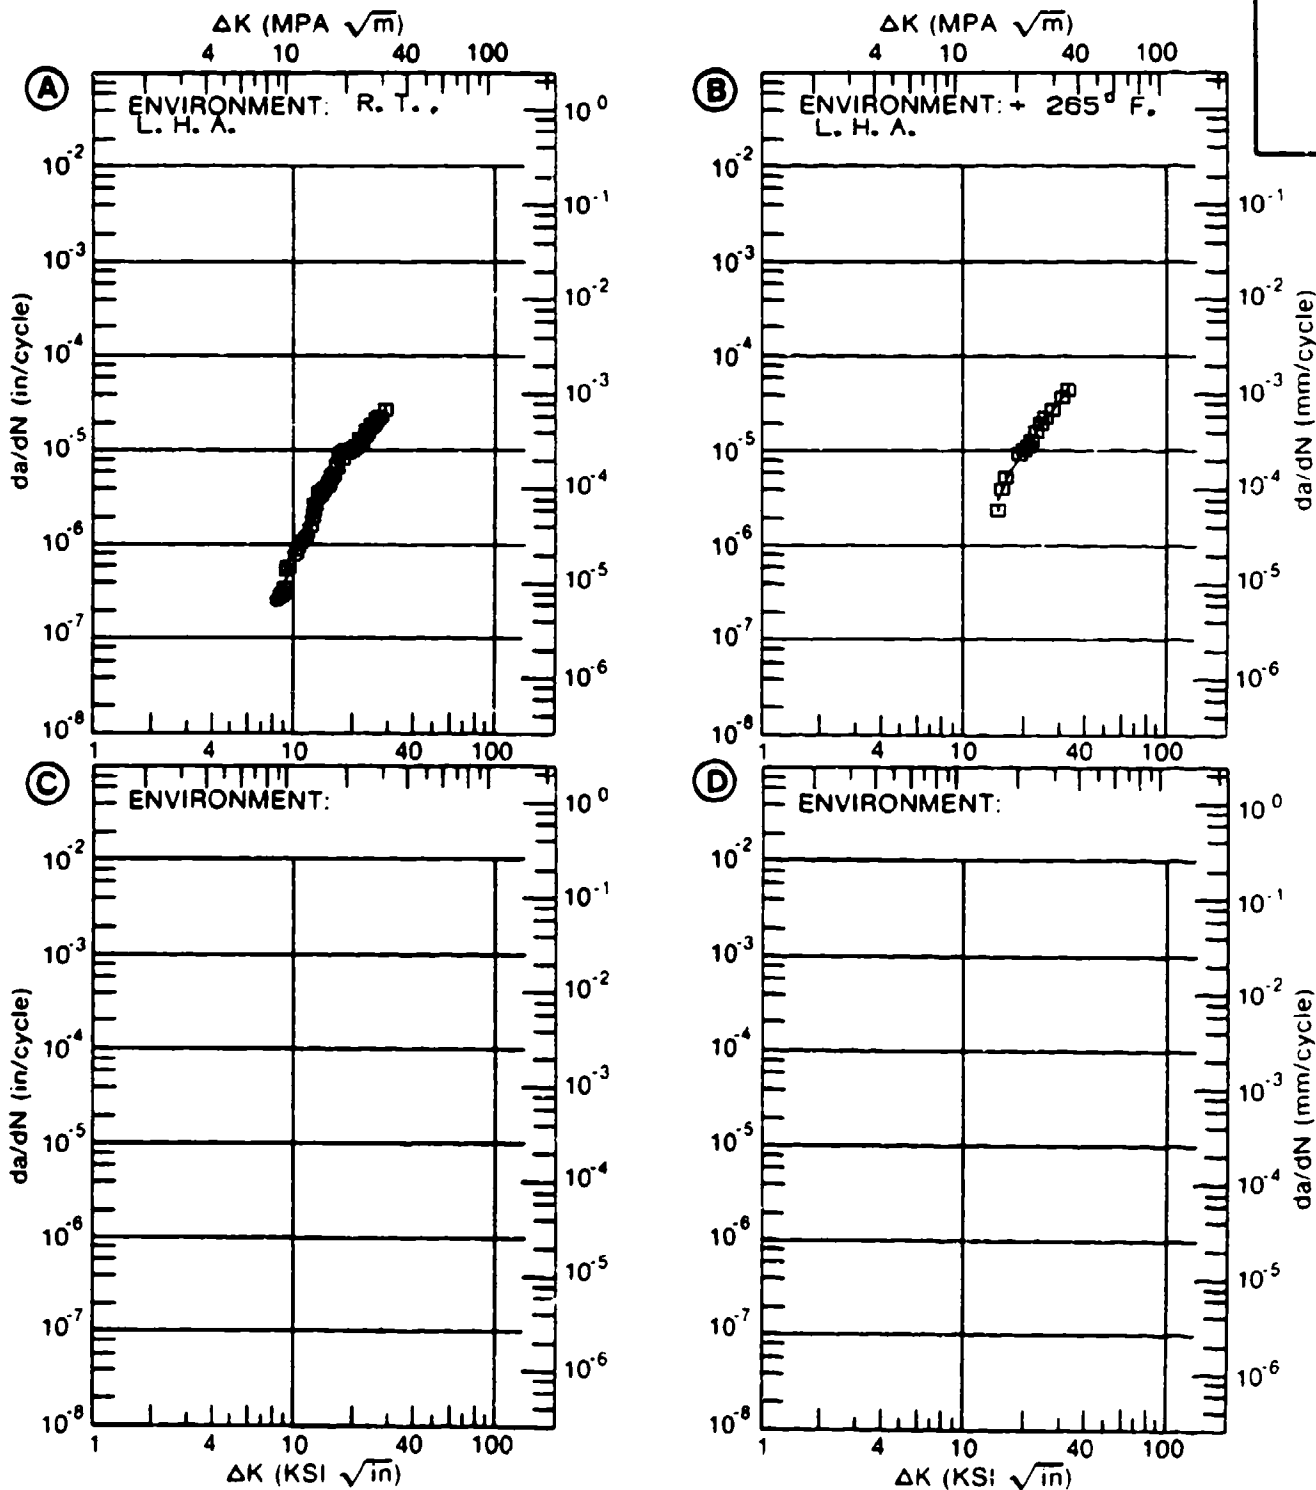


Figure 4.11.3.89

TABLE 4.11.3.90

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.90 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. J. P. 4	E=+ 150F S. T. W.	
DELTA K MIN	A: 24.00	14.4			
	B: 7.83		.107		
	C: 12.49			2.27	
	D:				
	8.00		.126		
	9.00		.308		
	10.00		.663		
	13.00		3.00	2.73	
	16.00		6.83	5.97	
	20.00		12.8	11.8	
	25.00	16.6	20.2	24.4	
	30.00	30.7		53.4	
	35.00	50.0			
	40.00	74.7			
DELTA K MAX	A: 41.69	84.3			
	B: 26.71		22.7		
	C: 33.71			102.	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		4.34	20.62	16.88	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1	1	

CONDITION/HT: RA
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 117.0- 121.0 KSI
 ULT. STRENGTH: 129.0- 135.0 KSI
 SPECIMEN THK: 0.992- 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837, 88579

TITAN.
 ALLOY
 TI-6AL-
 4V

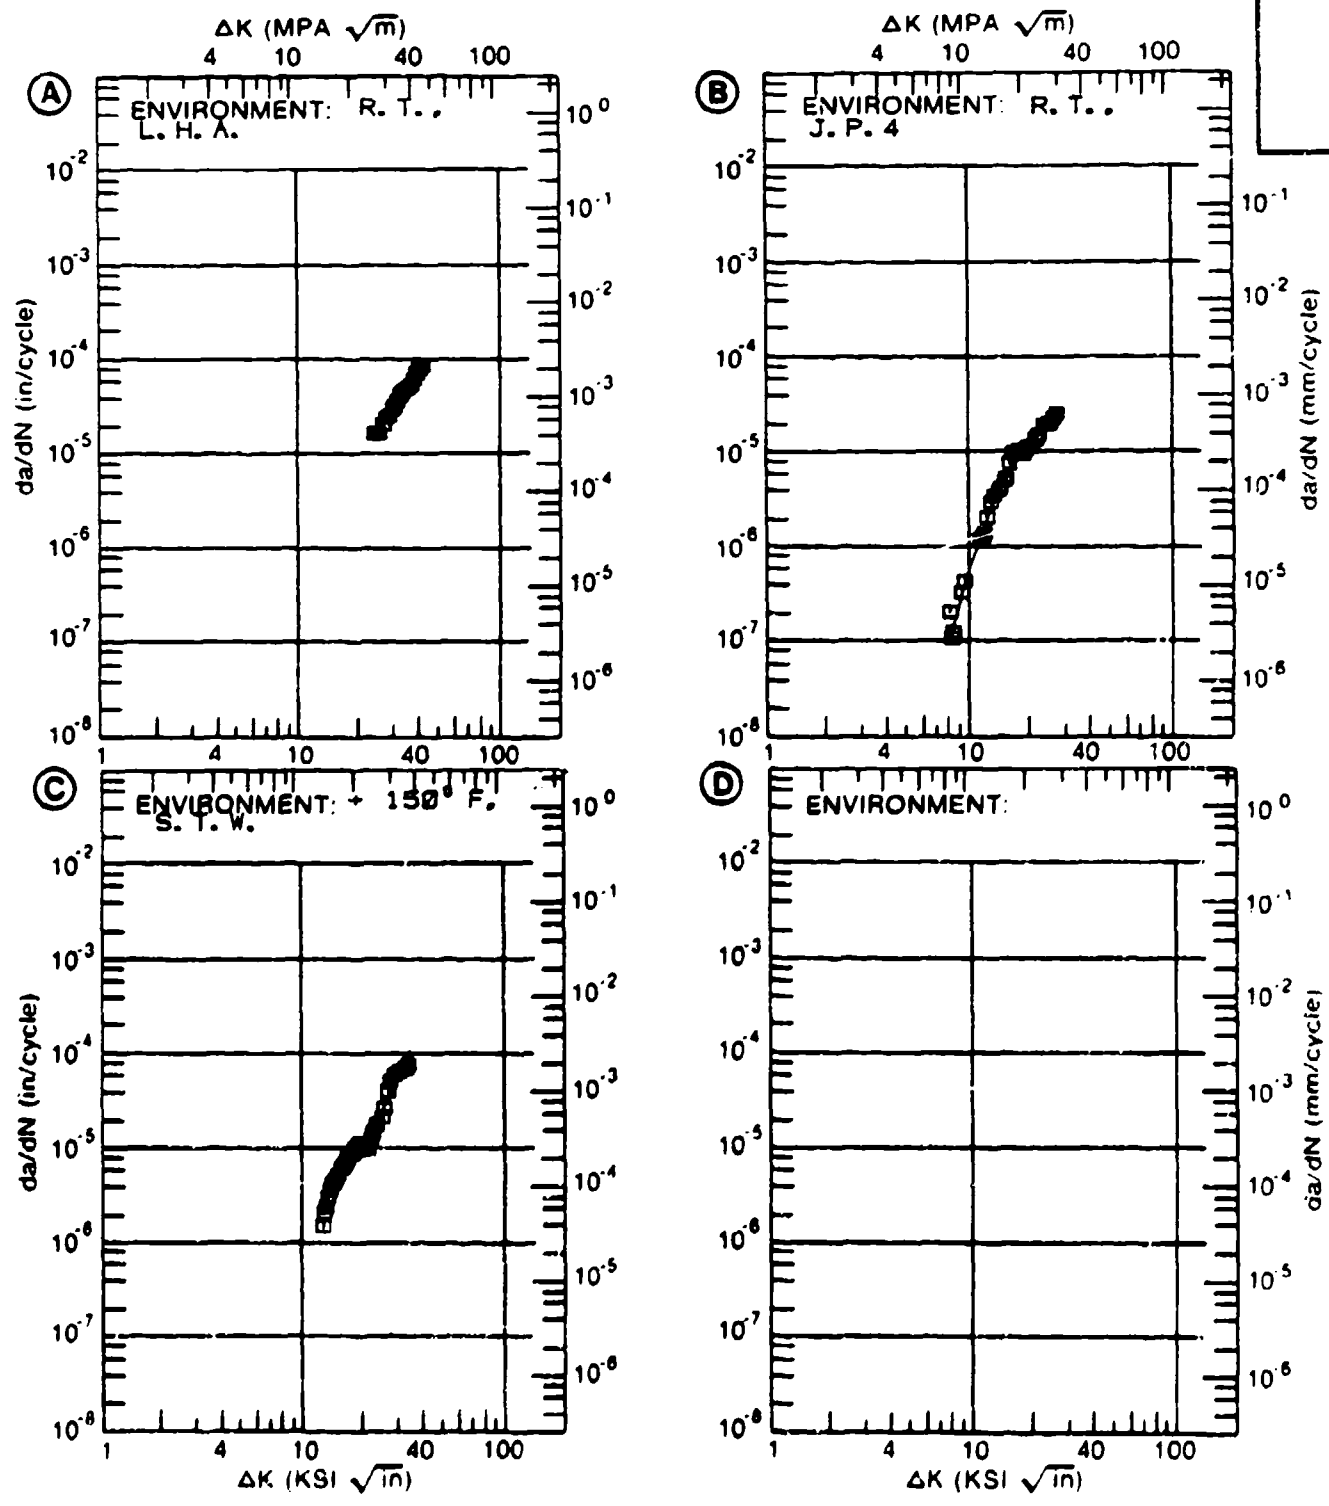


Figure 4.11.3.90

TABLE 4.11.3.91

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
 ΔK STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.91 INDICATING EFFECT
 OF FREQUENCY

MATERIAL: TITANIUM TI-6AL-4V
 CONDITION: RA
 ENVIRONMENT: R. T. , S. T. W.

DELTA K (KSI*IN**1/2)	DA/DN (10**+6 IN. /CYCLE)			
	A	B	C	D
	F(HZ)= 0.10		F(HZ)= 1.00	
MIN				
A: 11.17	1.07			
B: 8.35		.340		
C:				
D:				
9.00		.423		
10.00		.590		
13.00	2.24	1.52		
16.00	4.15	3.49		
20.00	11.0	8.98		
25.00	21.4	23.4		
30.00	49.0	50.6		
35.00		94.6		
40.00		158.		
50.00		344.		
60.00		591.		
MAX				
A: 32.56	89.8			
B: 66.77		772.		
C:				
D:				

ROOT MEAN SQUARE 12.74 58.58
 PERCENT ERROR

LIFE 0.0-0.5
 PREDICTION 0.5-0.8 2
 RATIO 0.8-1.25 1
 SUMMARY 1.25-2.0 2
 (NP/NA) >2.0

CONDITION/HT: RA
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 118.0- 124.0 KSI
 ULT. STRENGTH: 129.0- 138.0 KSI
 SPECIMEN THK: 0.988- 1.010"
 SPECIMEN WIDTH: 7.390- 7.400"
 REFERENCES: 88579, 85837

TITAN.
 ALLOY

TI-6AL-
 4V

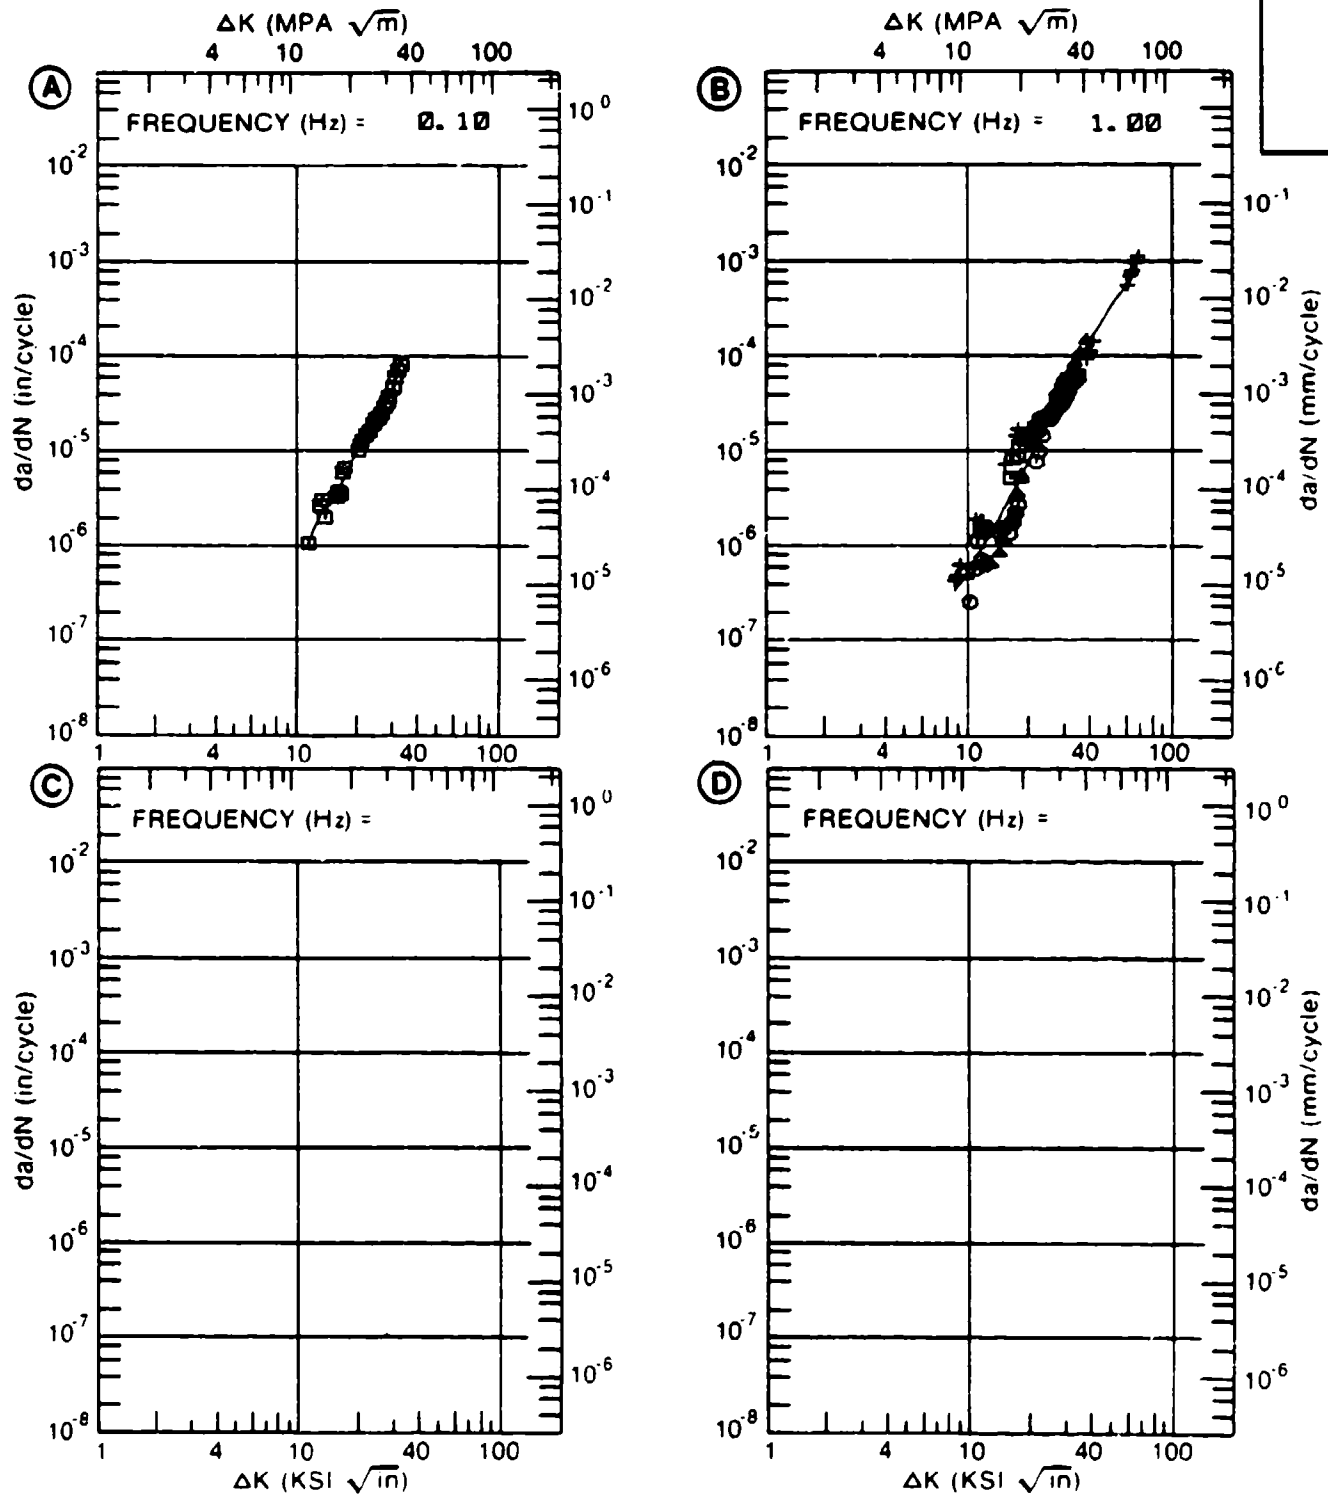


Figure 4.11.3.91

TABLE 4.11.3.92

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.92 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: RA

TI-6AL-4V

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A. 6HZ	E= R. T. J. P. 4 1HZ	E= R. T. S. T. W. 1HZ	
DELTA K	A: 8.94	.231			
MIN	B: 7.99		.226		
	C: 6.08			.0803	
	D:				
	7.00			.175	
	8.00		.226	.346	
	9.00	.244	.375	.604	
	10.00	.537	.717	.964	
	13.00	2.45	3.58	2.78	
	16.00	5.74	7.91	5.93	
	20.00	11.4	14.2	12.7	
	25.00	20.2		26.3	
	30.00	32.0		47.6	
	35.00	49.9		79.4	
	40.00	78.5		126.	
	50.00	208.		285.	
	60.00	609.		592.	
	70.00			1160.	
DELTA K	A: 63.39	893.			
MAX	B: 24.76		25.7		
	C: 71.06			1242.	
	D:				
ROOT MEAN SQUARE		27.79	12.87	33.61	
PERCENT ERROR					

LIFE	0.0-0.5			
PREDICTION	0.5-0.8	1		1
RATIO	0.8-1.25	1	1	
SUMMARY	1.25-2.0	1		1
(NP/NA)	>2.0			

CONDITION/HT: RA
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 122.0- 125.0 KSI
 ULT. STRENGTH: 134.0- 135.0 KSI
 SPECIMEN THK: 0.501- 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837, 88579

TITAN.
 ALLOY

TI-6AL-
 4V

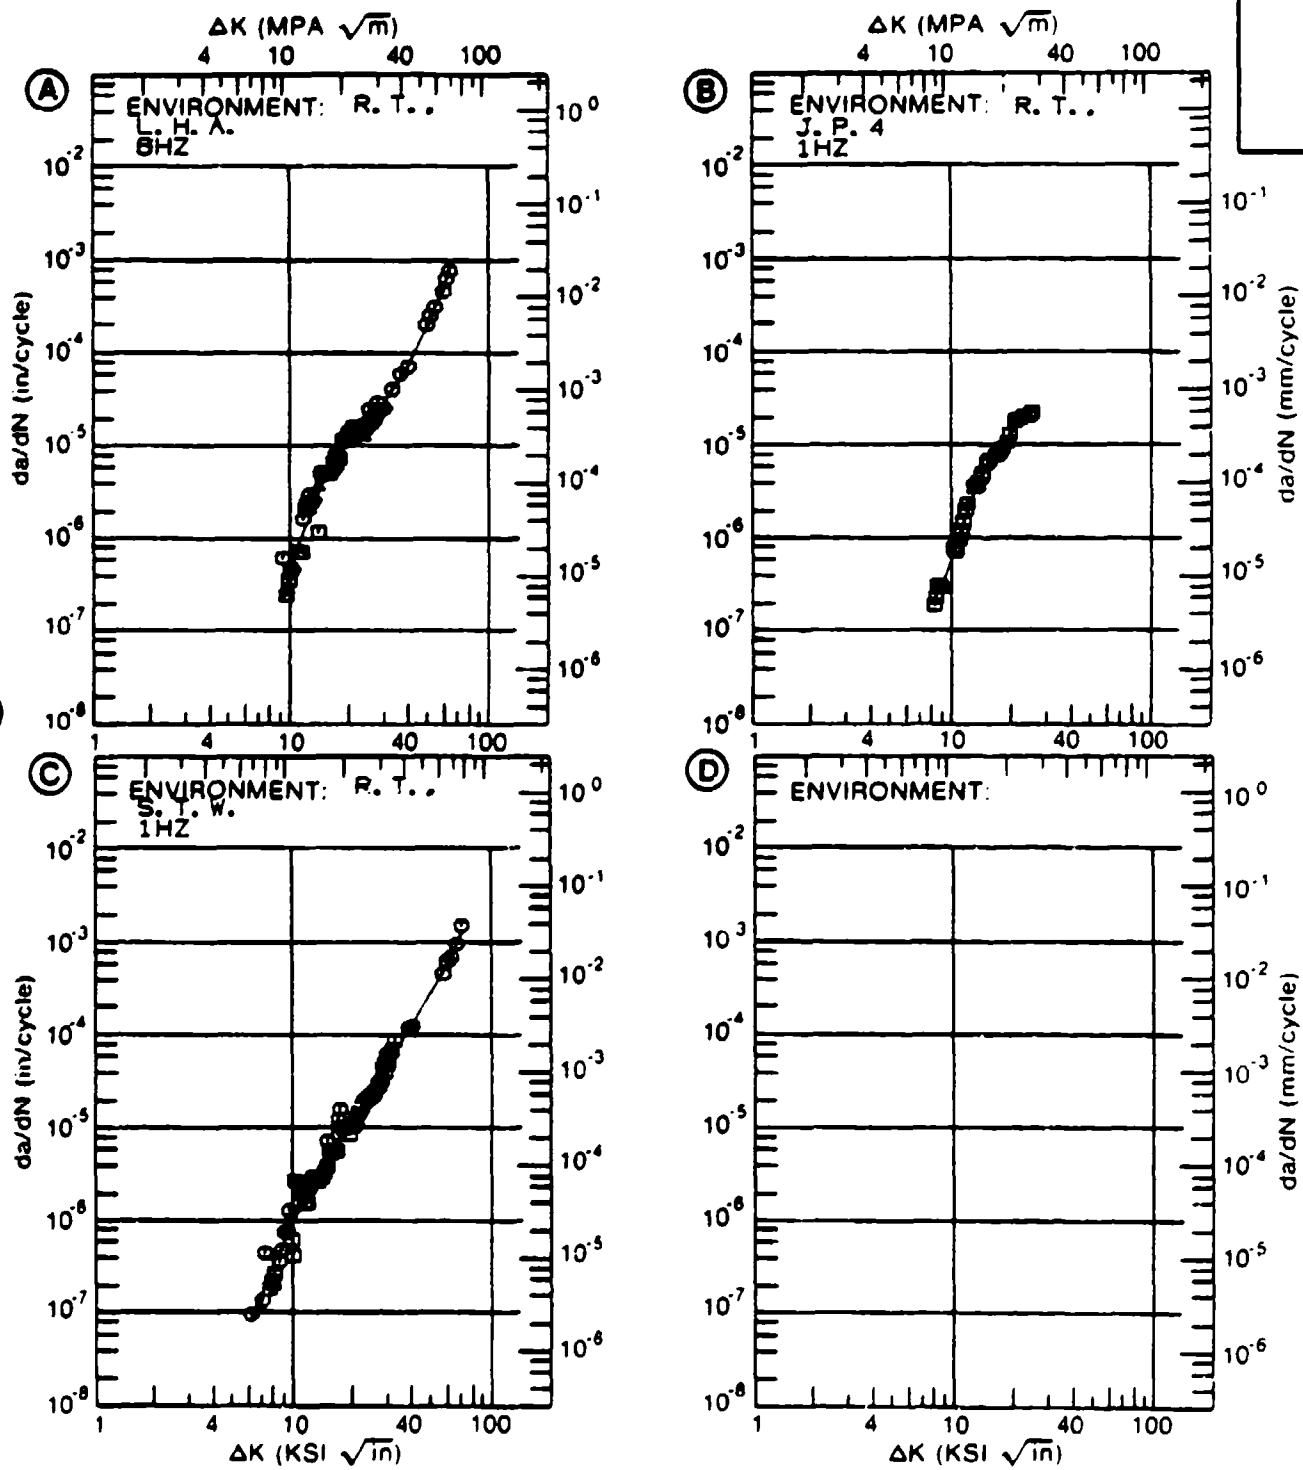


Figure 4.11.3.92

TABLE 4.11.3.93

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.93 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		F. C. S.			
DELTA K	A: 13.81	3.33			
MIN	B:				
	C:				
	D:				
	16.00	4.56			
	20.00	8.72			
	25.00	16.8			
	30.00	24.7			
DELTA K	A: 30.21	24.9			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		4.69			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 117.0 KSI
 ULT. STRENGTH: 133.0 KSI
 SPECIMEN THK: 1.390"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: 88579

TITAN.
 ALLOY

TI-6AL-
 4V




Figure 4.11.3.93

TABLE 4.11.3.94

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.94 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		L. H. A.			
DELTA K	A: 11.70	1.48			
MIN	B:				
	C:				
	D:				
	13.00	2.98			
DELTA K	A: 15.81	5.79			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		10.94			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 121.0 KSI
 ULT. STRENGTH: 135.0 KSI
 SPECIMEN THK: 1.013"
 SPECIMEN WIDTH: 7.380"
 REFERENCES: 85837

TITAN.
 ALLOY

TI-6AL-
 4V

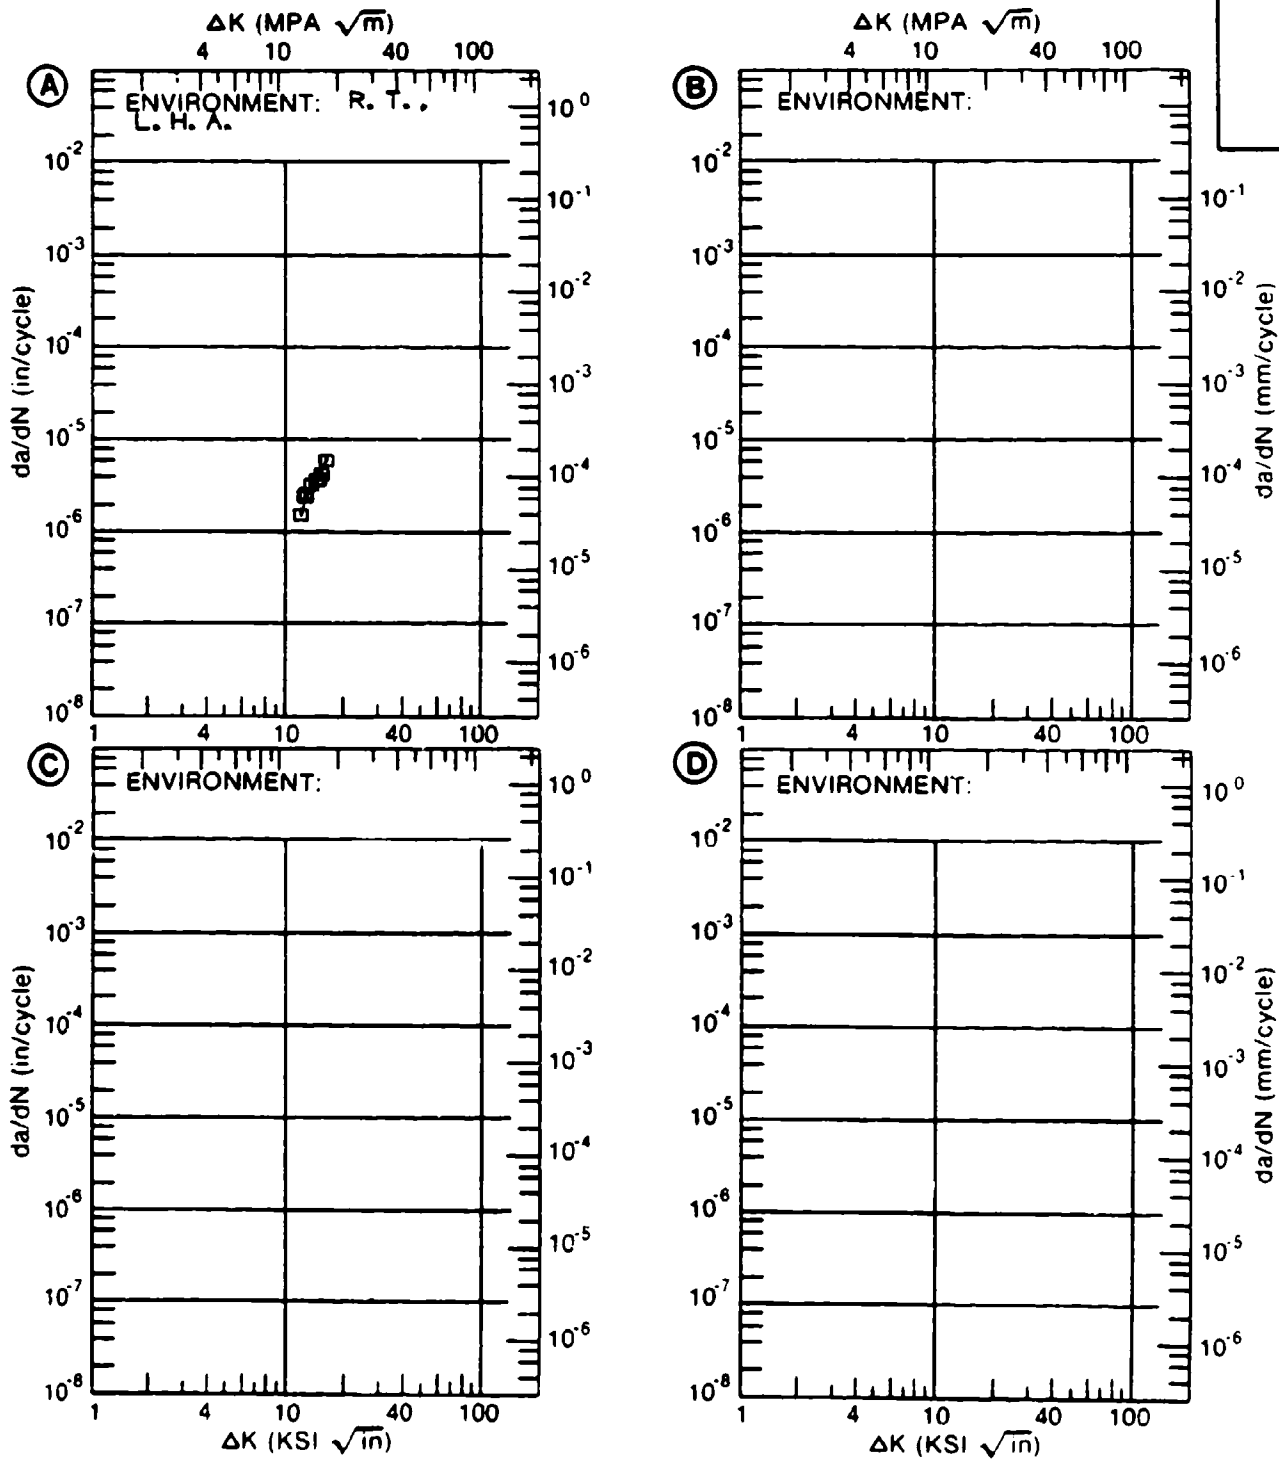


Figure 4.11.3.94

TABLE 4.11.3.95

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.95 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.	E=+ 150F		
		L. H. A.	S. T. W.		
		6HZ	1HZ		
DELTA K	A: 15.66	1.74			
MIN	B: 12.77		.99		
	C:				
	D:				
	13.00		1.06		
	16.00	2.12	2.71		
	20.00	7.80	9.37		
	25.00	17.5	31.9		
	30.00		67.8		
DELTA K	A: 29.18	45.5			
MAX	B: 34.28		93.1		
	C:				
	D:				
ROOT MEAN SQUARE		12.60	11.76		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 119.0- 122.0 KSI
 ULT. STRENGTH: 131.0- 133.0 KSI
 SPECIMEN THK: 0.898- 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837, 88579

TITAN.
 ALLOY

TI-6AL-
 4V

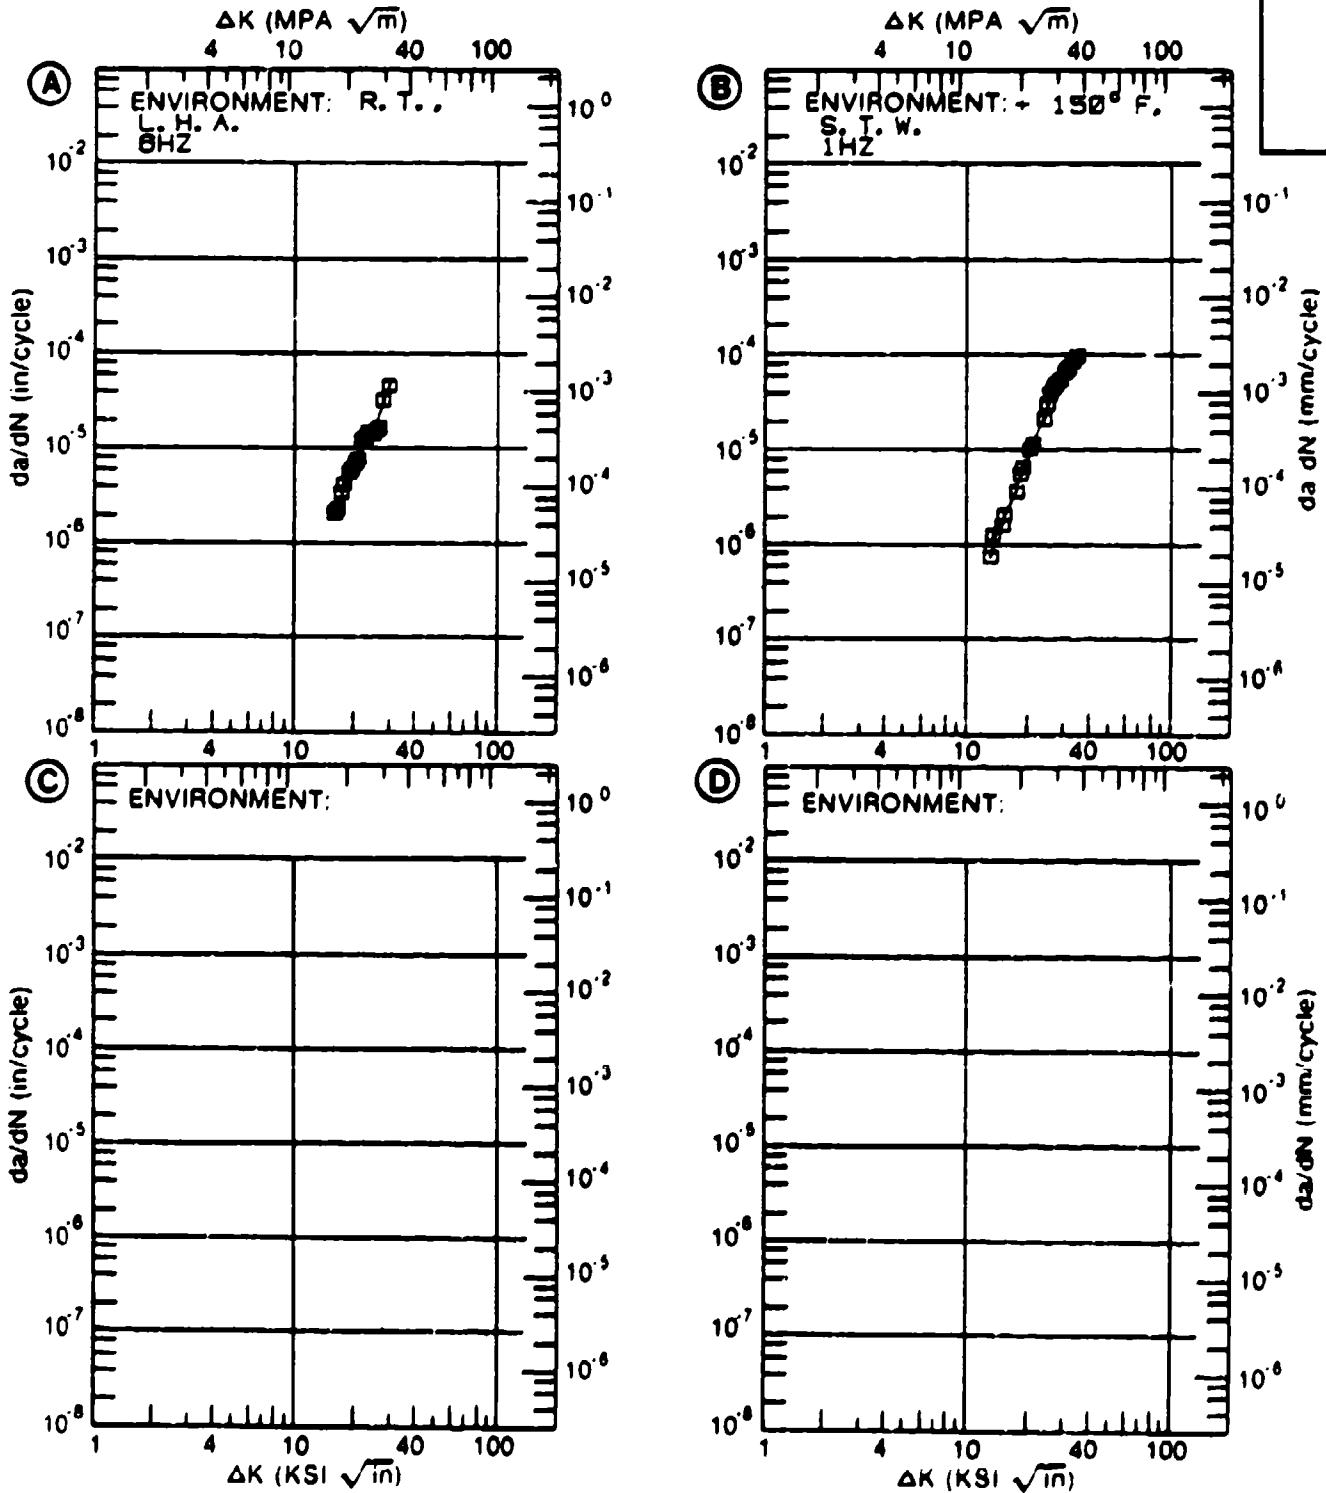


Figure 4.11.3.95

TABLE 4.11.3.96

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.96 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: RA

TI-6AL-4V

DELTA K (KSI*IN**1/2)	DA/DN (10**6 IN./CYCLE)			
	A	B	C	D
	E= R. T. S. T. W.			
DELTA K MIN	A: 13.93	.788		
	B: 16.00	2.13		
	C: 20.00	8.98		
	D: 25.00	27.5		
DELTA K MAX	A: 26.33	33.2		
	B:			
	C:			
	D:			

ROOT MEAN SQUARE 10.04
PERCENT ERROR

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	
RATIO	0.8-1.25	1
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: RA
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 126.0 KSI
 ULT. STRENGTH: 135.0 KSI
 SPECIMEN THK: 0.997"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837

TITAN.
 ALLOY

TI-6AL-
 4V

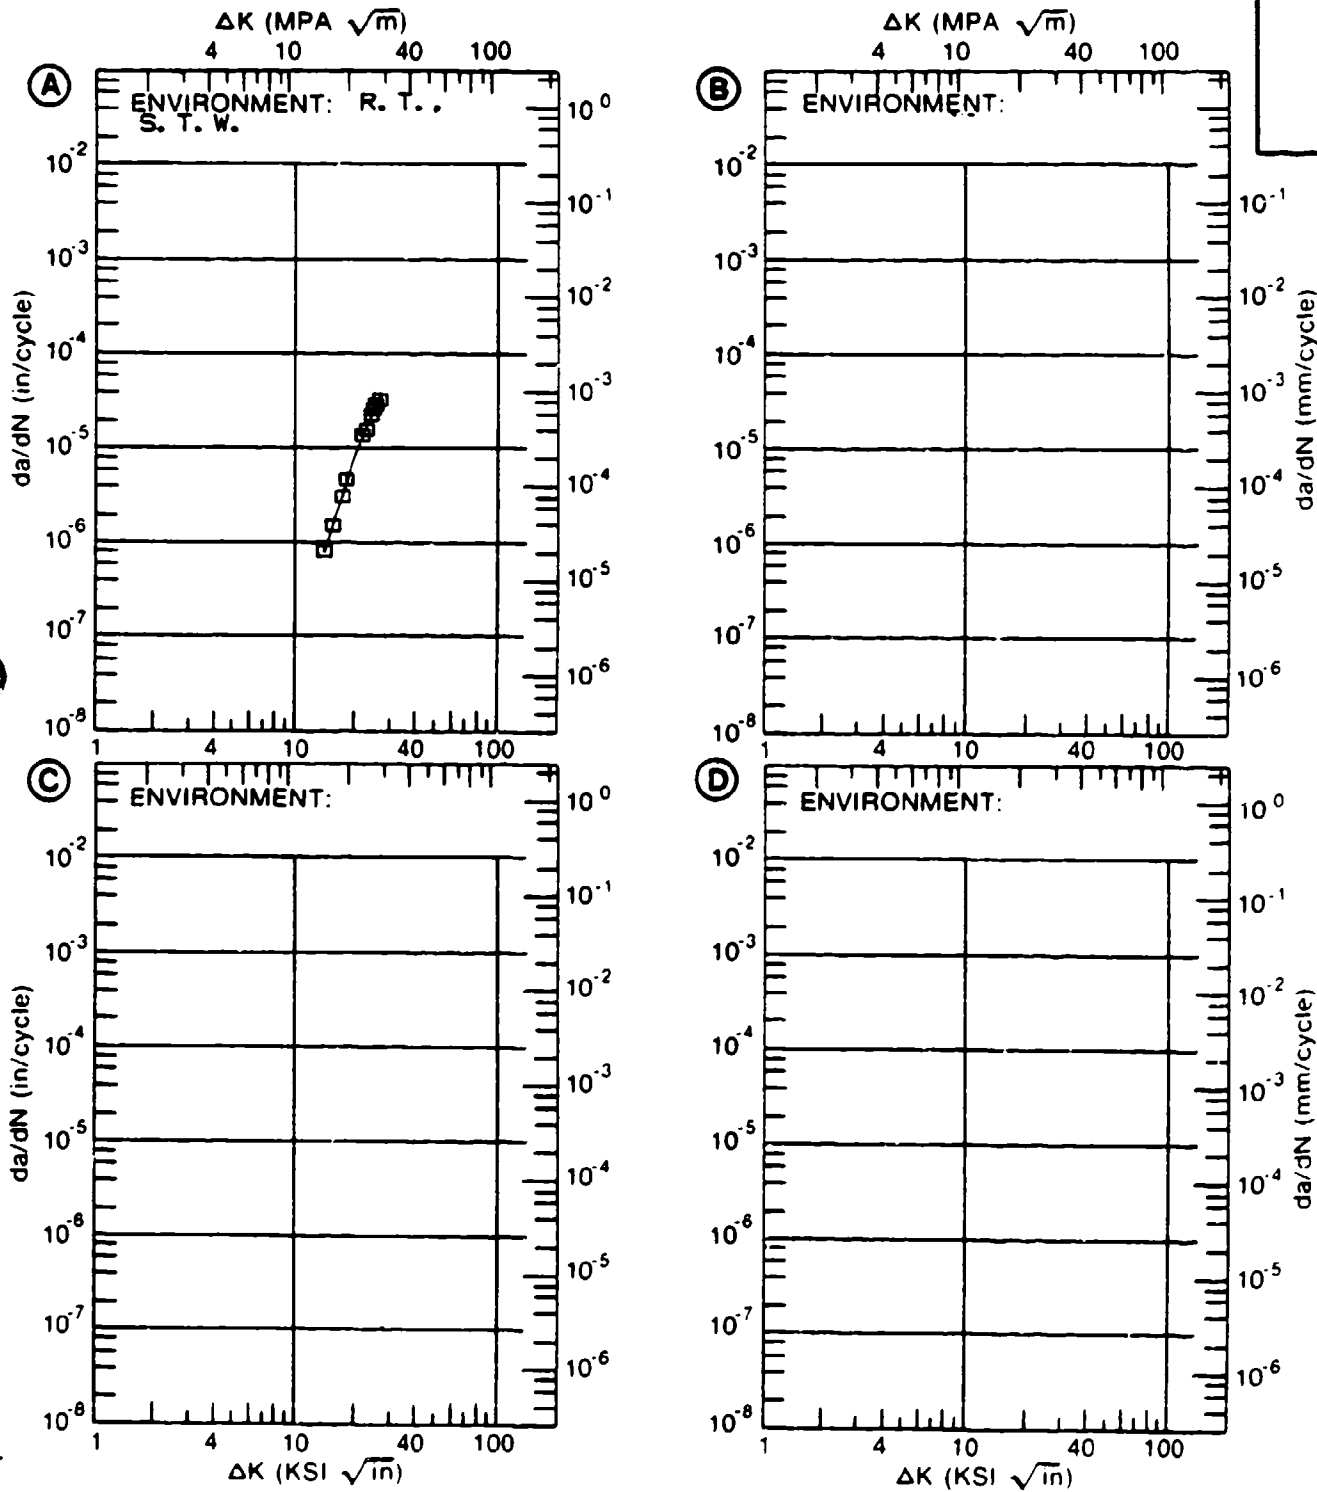


Figure 4.11.3.96

TABLE 4.11.3.97

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.97 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: RA
ENVIRONMENT: R. T. , S. T. W.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.08			
DELTA K	A: 7.80	.142			
MIN	B:				
	C:				
	D:				
	8.00	.215			
	9.00	.594			
	10.00	.778			
	13.00	1.31			
	16.00	3.25			
	20.00	13.4			
	25.00	37.5			
DELTA K	A: 28.44	54.6			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 22.56
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: RA
 FORM: 2.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T. . S. T. W.

YIELD STRENGTH: 120.0 KSI
 ULT. STRENGTH: 131.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 88578

TITAN.
 ALLOY

TI-6AL-
 4V

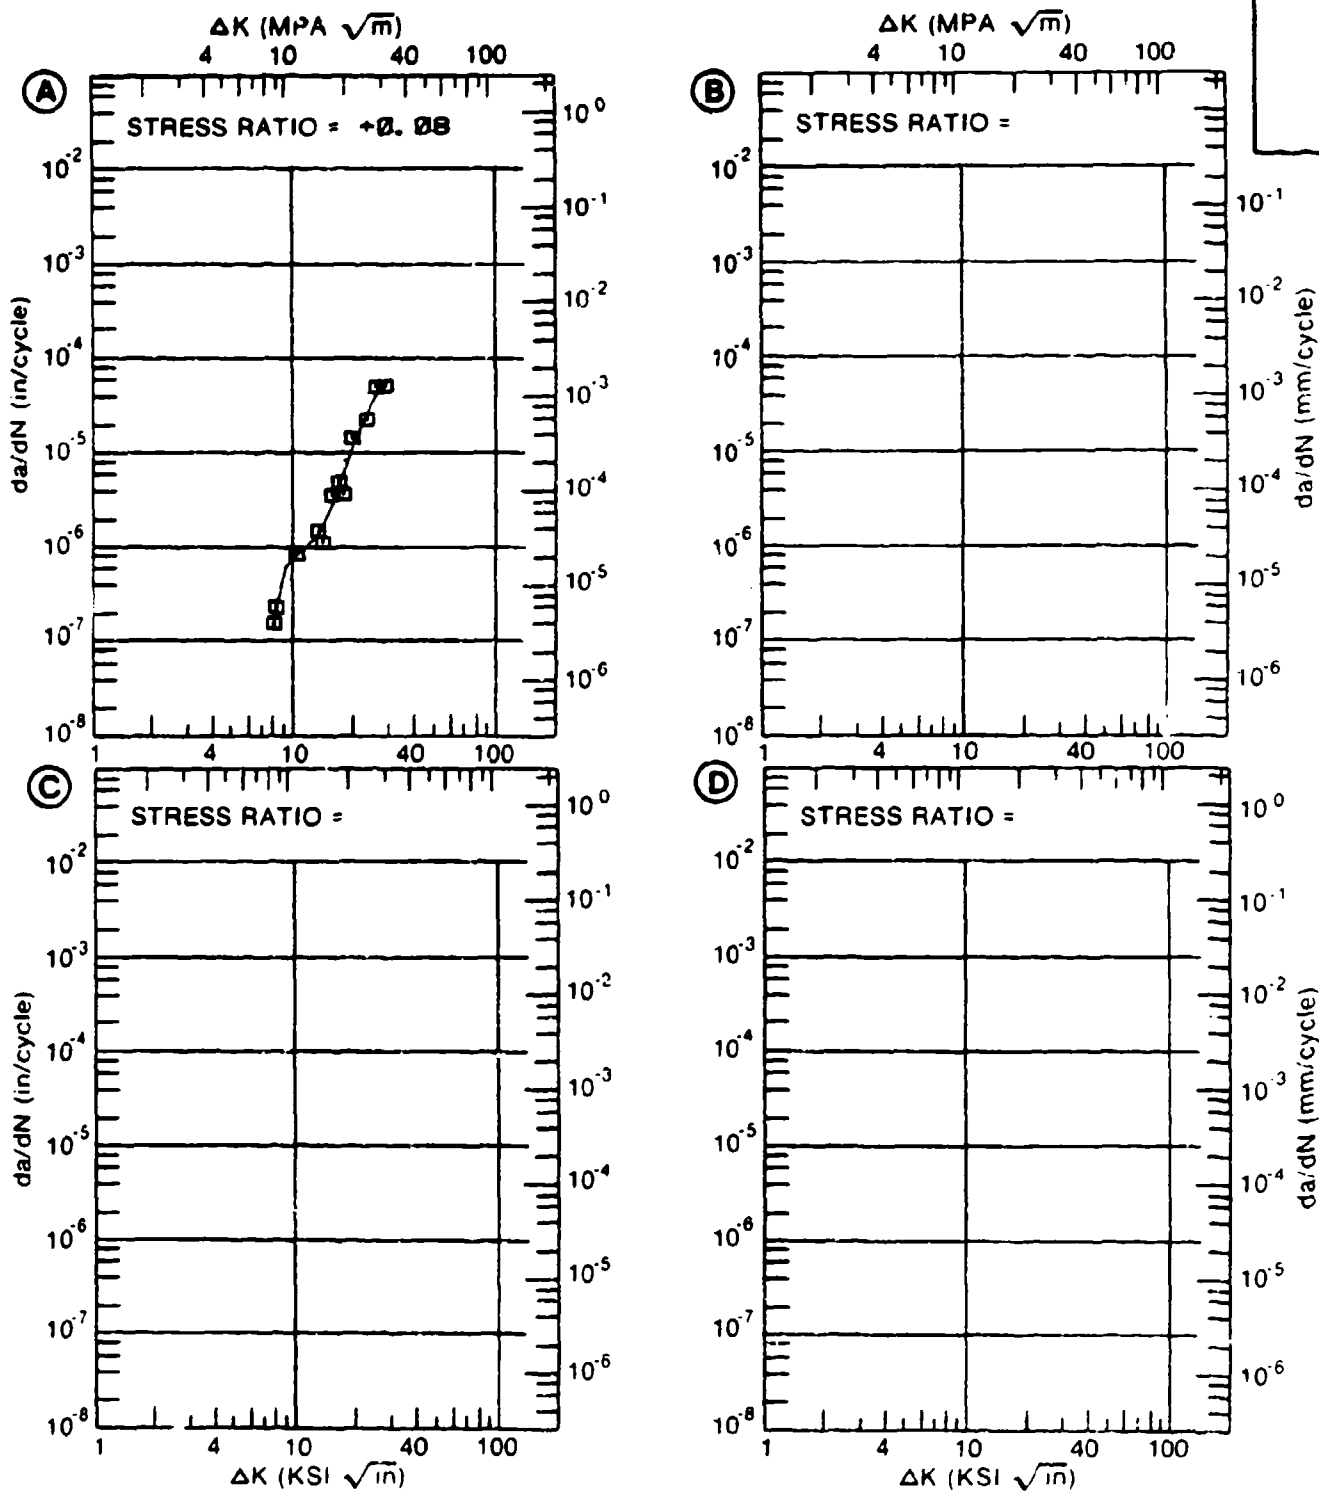


Figure 4.11.3.97

TABLE 4.11.3.98

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.98 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A. 6HZ	E= R. T. S. T. W. 1HZ		
DELTA K	A: 11.40	.581			
MIN	B: 11.39		.991		
	C:				
	D:				
	12.00	.811	1.70		
	12.00	4.76	3.96		
	20.00	10.4	9.34		
	25.00	19.9	28.1		
	30.00	34.8			
DELTA K	A: 32.46	42.9			
MAX	B: 27.68		34.6		
	C:				
	D:				
ROOT MEAN SQUARE		13.29	15.40		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	2		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 2.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 122.0 KSI
 ULT. STRENGTH: 136.0 KSI
 SPECIMEN THK: 0.990- 1.000"
 SPECIMEN WIDTH: 7.390- 7.400"
 REFERENCES: 88579

TITAN. ALLOY
TI-6AL- 4V

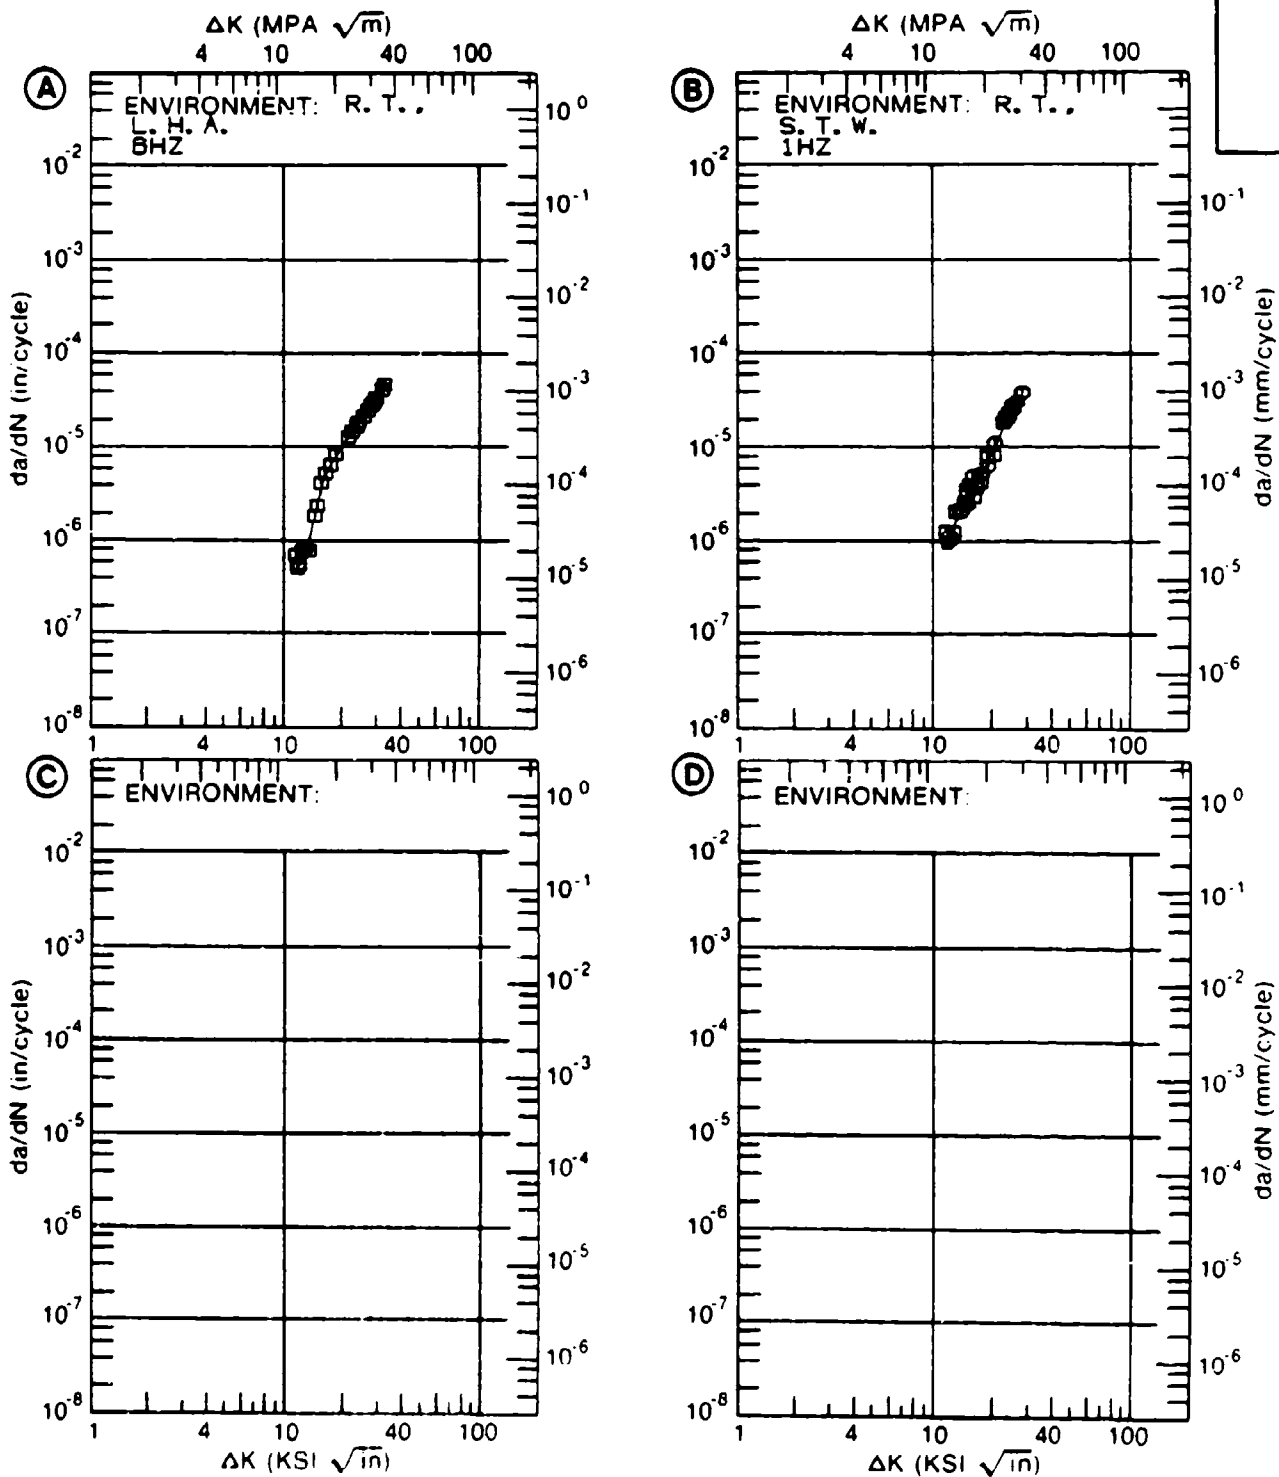


Figure 4.11.3.98

TABLE 4.11.3.99

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.99 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. L. H. A. 6HZ	E= R. T. S. T. W. 1HZ		
DELTA K	A: 10.70	.357			
MIN	B: 10.73		.743		
	C:				
	D:				
	13.00	1.12	1.37		
	16.00	3.51	3.28		
	20.00	9.89	9.12		
	25.00	20.7	23.1		
	30.00		40.6		
DELTA K	A: 29.26	27.4			
MAX	B: 31.56		45.4		
	C:				
	D:				
ROOT MEAN SQUARE		9.23	15.54		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8		1		
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 2.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: ± 0.08
 FREQUENCY:

YIELD STRENGTH: 122.0 KSI
 ULT. STRENGTH: 135.0 KSI
 SPECIMEN THK: 0.990- 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 98579

TITAN.
 ALLOY

TI-6AL-
 4V

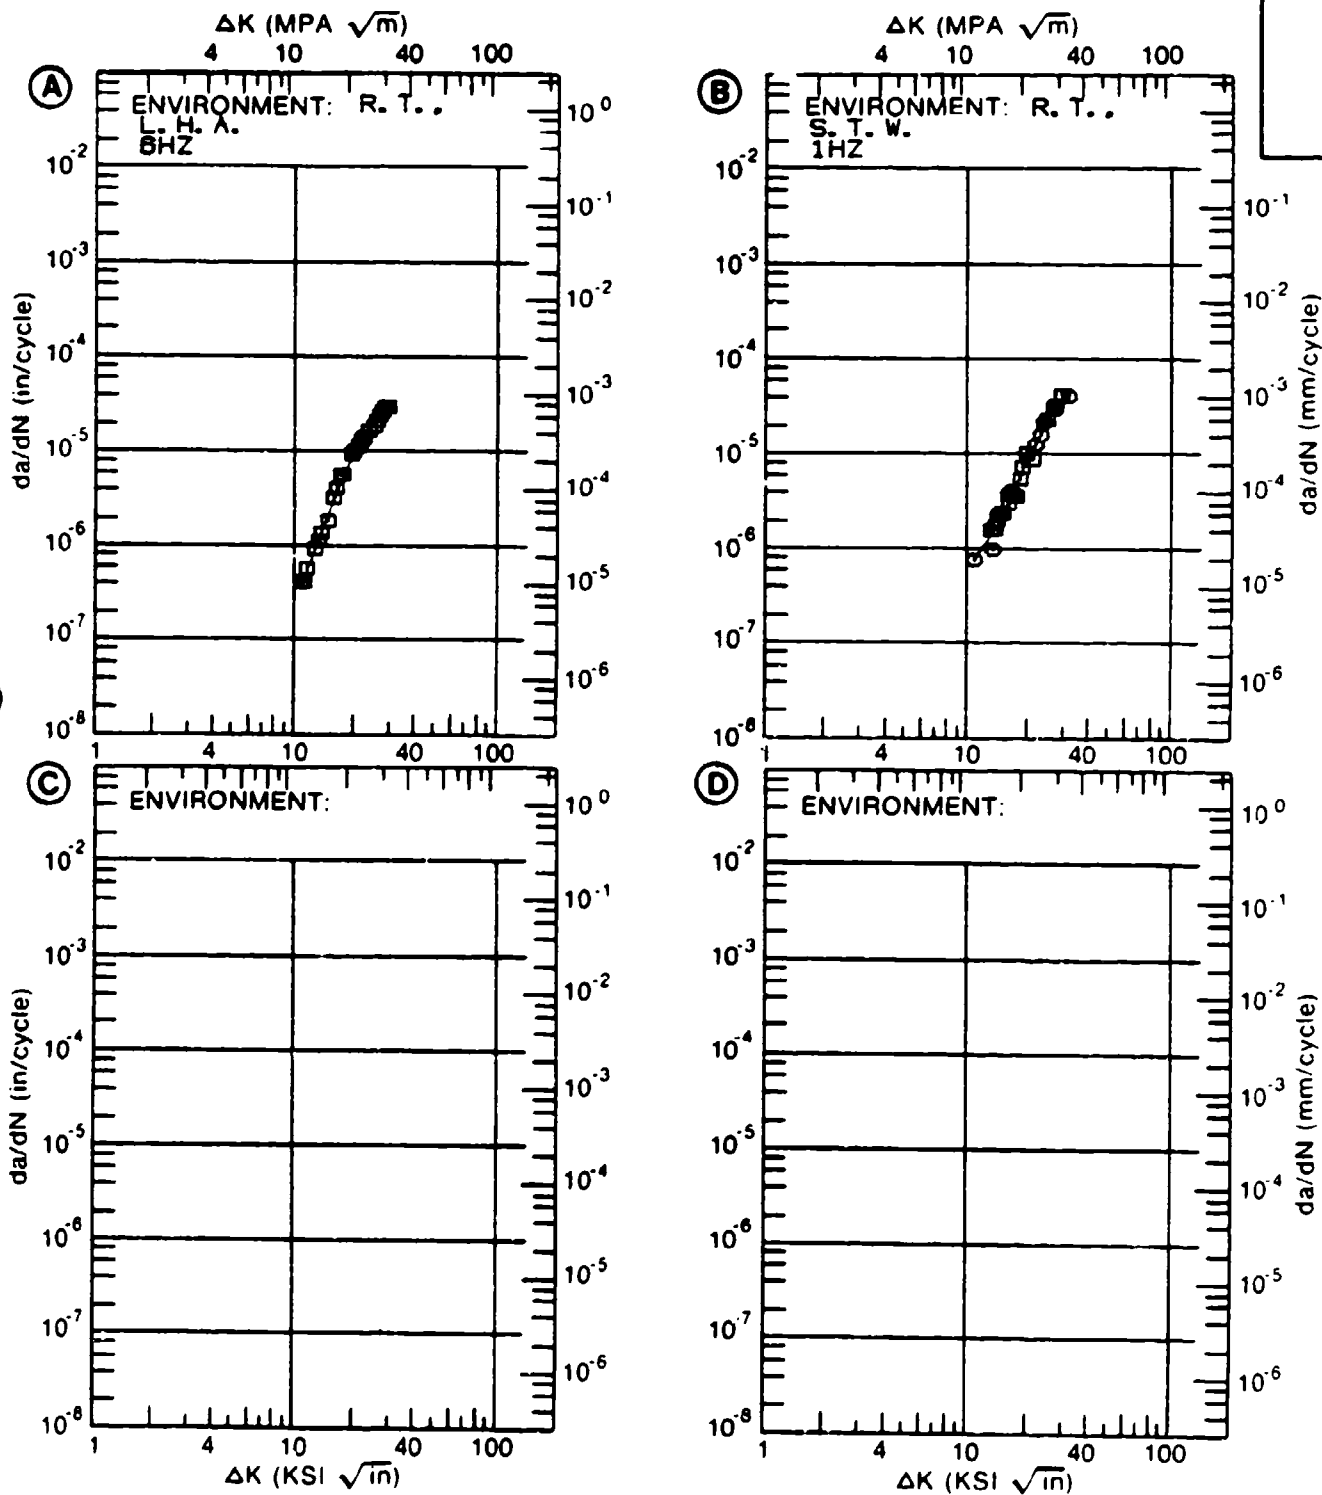


Figure 4.11.3.99

TABLE 4.11.3.100

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.100 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: RA

DELTA K (KSI*IN**1/2)	DA/DN (10**6 IN. /CYCLE)			
	A	B	C	D
	E= R. T. L. H. A.			
DELTA K A: 18.54	2.02			
MIN B:				
C:				
D:				
20.00	3.34			
25.00	10.6			
30.00	21.5			
35.00	36.3			
40.00	57.6			
50.00	145.			
60.00	405.			
DELTA K A: 62.29	521.			
MAX B:				
C:				
D:				

ROOT MEAN SQUARE 8.69
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: RA
 FORM: 3.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 118.0 KSI
 ULT. STRENGTH: 129.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 6.000"
 REFERENCES 88578

TITAN.
 ALLOY

TI-6AL-
 4V

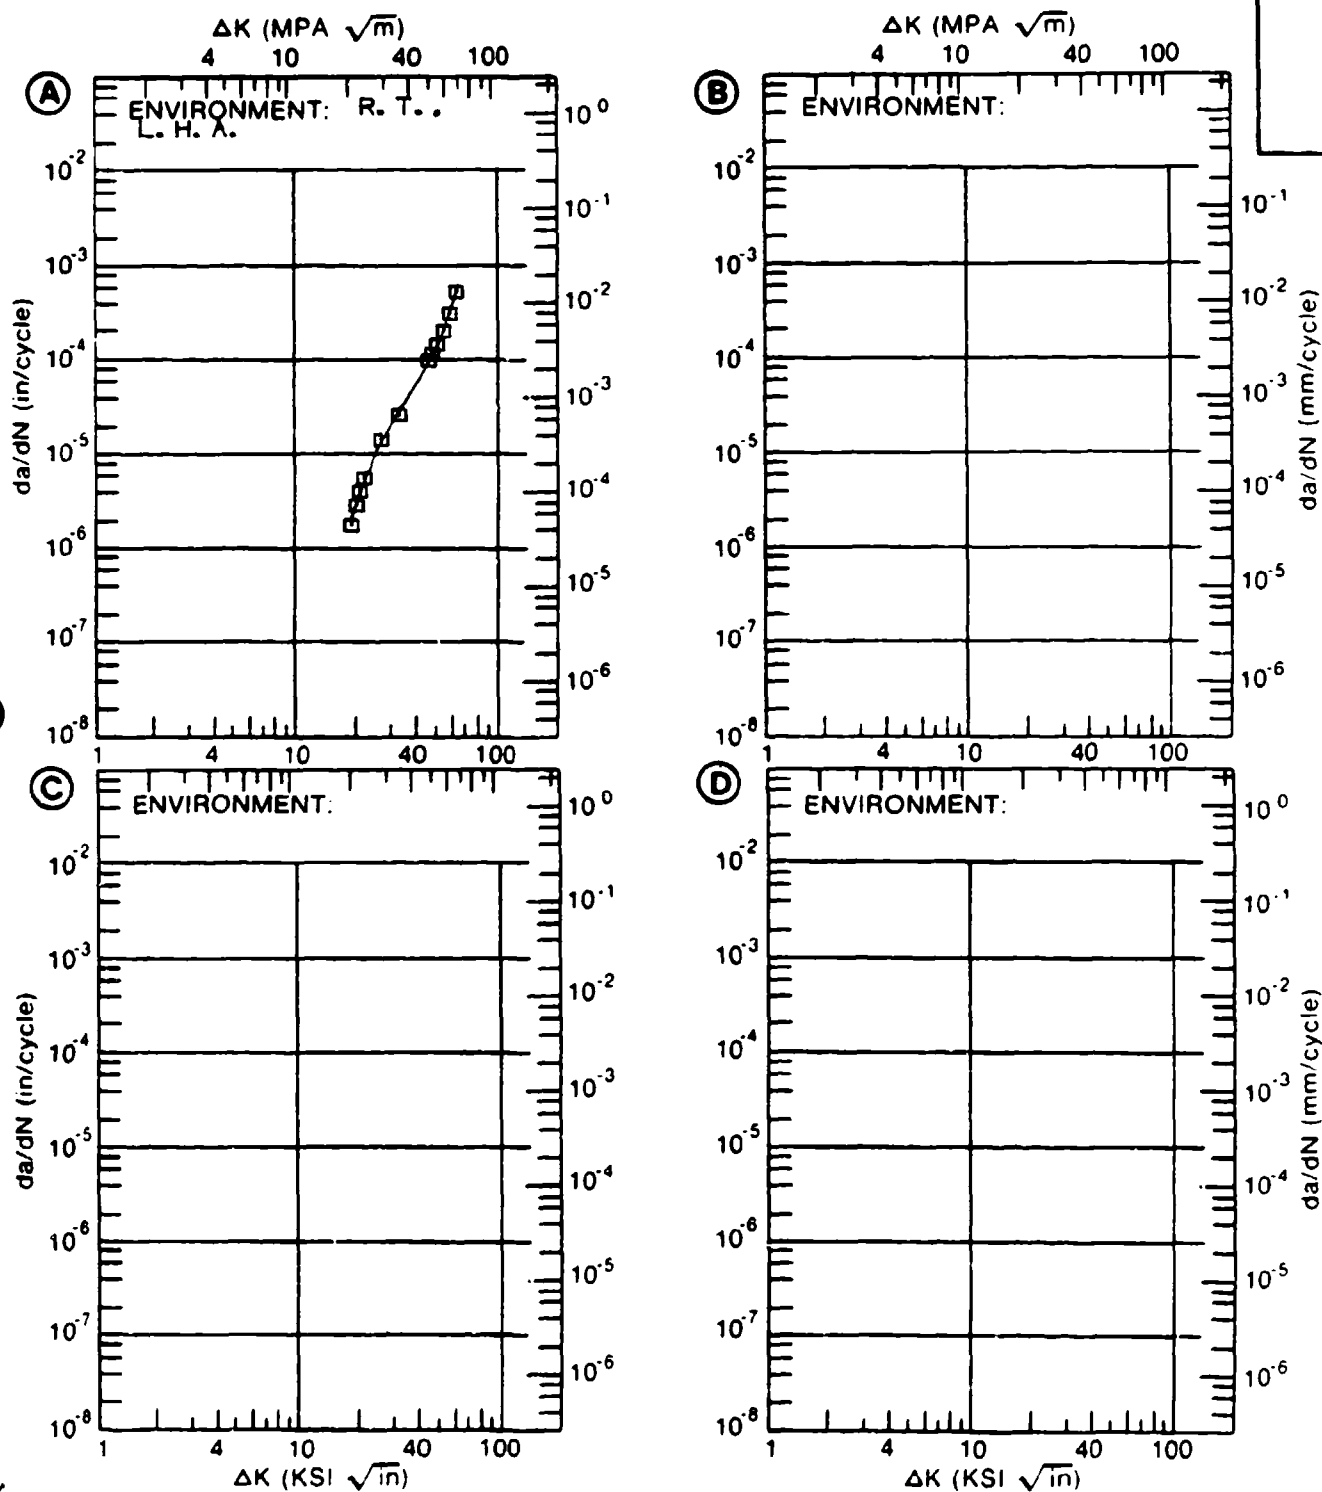


Figure 4.11.3.100

TABLE 4.11.3.101

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.101 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: RA
ENVIRONMENT: R. T. , S. T. W.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.08			
DELTA K MIN	A: 6.72	.356			
	B:				
	C:				
	D:				
	7.00	.384			
	8.00	.573			
	9.00	.957			
10.00	1.65				
13.00	7.24				
16.00	20.0				
20.00	36.8				
DELTA K MAX	A: 21.08	38.2			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 9.22
PERCENT ERROR

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	
RATIO	0.8-1.25	1
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: RA
 FORM: FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 123.0 KSI
 ULT. STRENGTH: 136.0 KSI
 SPECIMEN THK: 0.000"
 SPECIMEN WIDTH: 0.000"
 REFERENCES: 00578

TITAN.
 ALLOY
 TI-6AL-
 4V

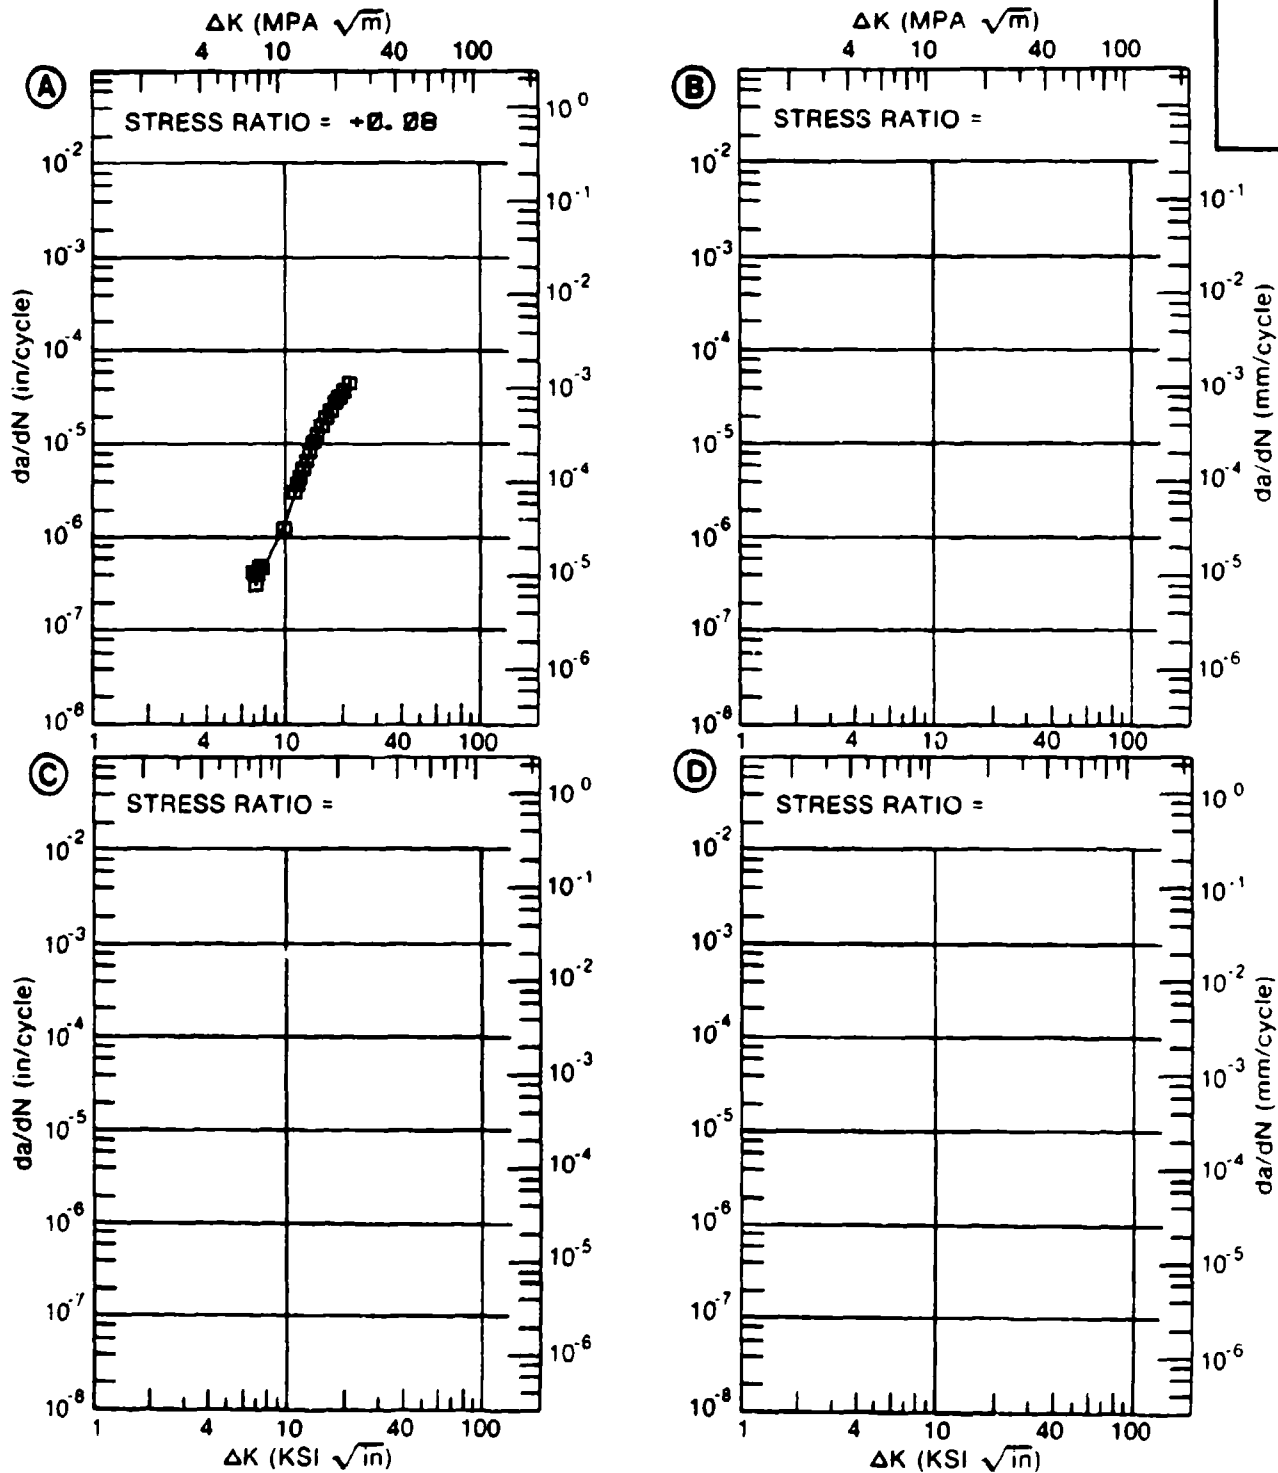


Figure 4.11.3.101

TABLE 4.11.3.102

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.102 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: RA
ENVIRONMENT: R. T. , S. T. W.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.08			
DELTA K MIN	A: 10.96	1.07			
	B:				
	C:				
	D:				
	13.00	2.50			
	16.00	6.47			
	20.00	16.1			
	25.00	36.1			
30.00	64.4				
35.00	99.4				
40.00	139.				
50.00	225.				
DELTA K MAX	A: 54.52	264.			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 22.85
PERCENT ERROR

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	
RATIO	0.8-1.25	1
SUMMARY	1.25-2.0	1
(NP/NA)	>2.0	

CONDITION/HT: RA
FORM: FORGING
SPECIMEN TYPE: CT
ORIENTATION: T-L
FREQUENCY: 1.00 HZ
ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 110.0 - 124.0 KSI
ULT. STRENGTH: 132.0 - 136.0 KSI
SPECIMEN THK: 0.010 - 1.010"
SPECIMEN WIDTH: 0.000"
REFERENCES 00579

TITAN.
ALLOY

TI-6AL-
4V

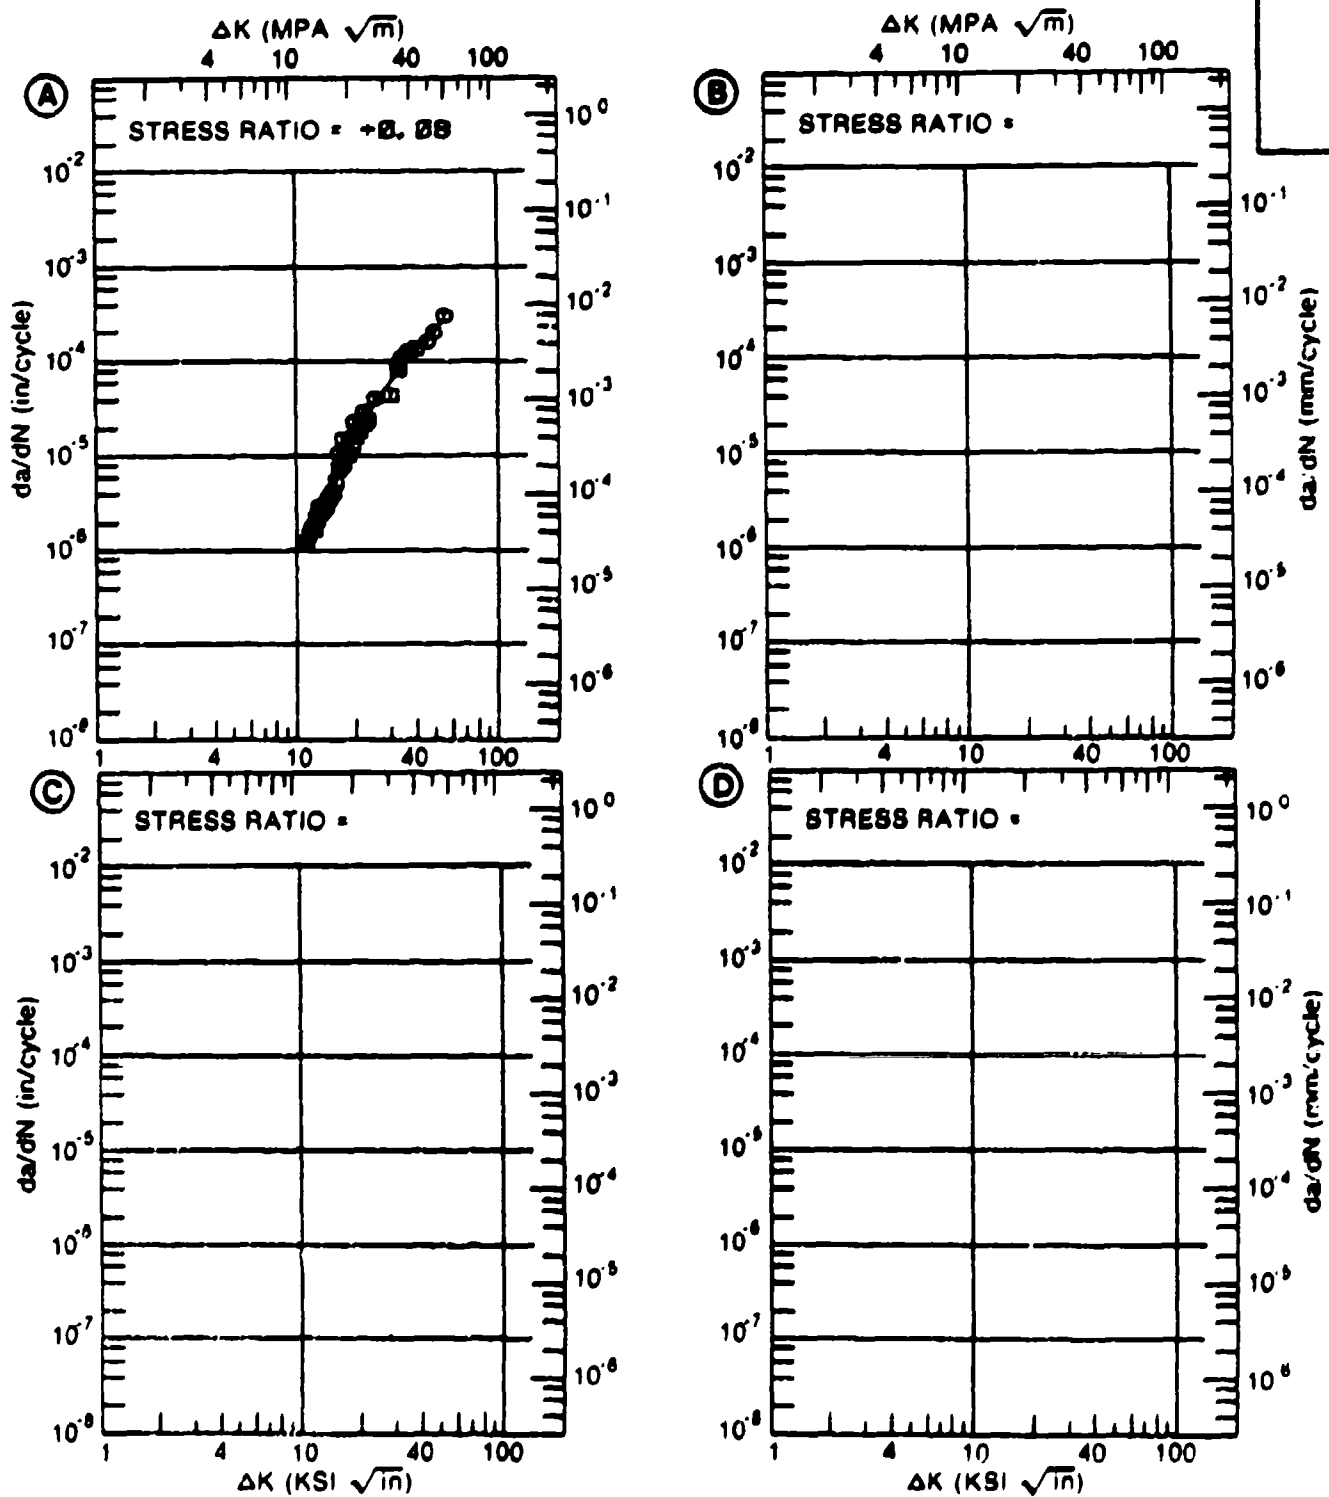


Figure 4.11.3.102

TABLE 4.11.3.103

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.10 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: RA
ENVIRONMENT: R. T. , L. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30		
DELTA K	A: 10.40	.132			
MIN	B: 9.44		.866		
	C:				
	D:				
	10.00		1.22		
	13.00	.618	4.26		
	16.00	1.93	8.77		
	20.00	6.76	16.2		
	25.00	13.9	28.2		
	30.00	23.3	45.4		
	35.00		72.4		
	40.00		117.		
	50.00		324.		
DELTA K	A: 34.94	36.0			
MAX	B: 57.20		710.		
	C:				
	D:				
ROOT MEAN SQUARE		12.27	8.17		
PERCENT ERROR					

LIFE	0.0-0.5		
PREDICTION	0.5-0.8		
RATIO	0.8-1.25		1
SUMMARY	1.25-2.0	1	
(NP/NA)	>2.0		

CONDITION/HT: RA
 FORM: 4.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 8.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 121.0 KSI
 ULT. STRENGTH: 132.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 98579

TITAN.
 ALLOY

TI-6AL-
 4V

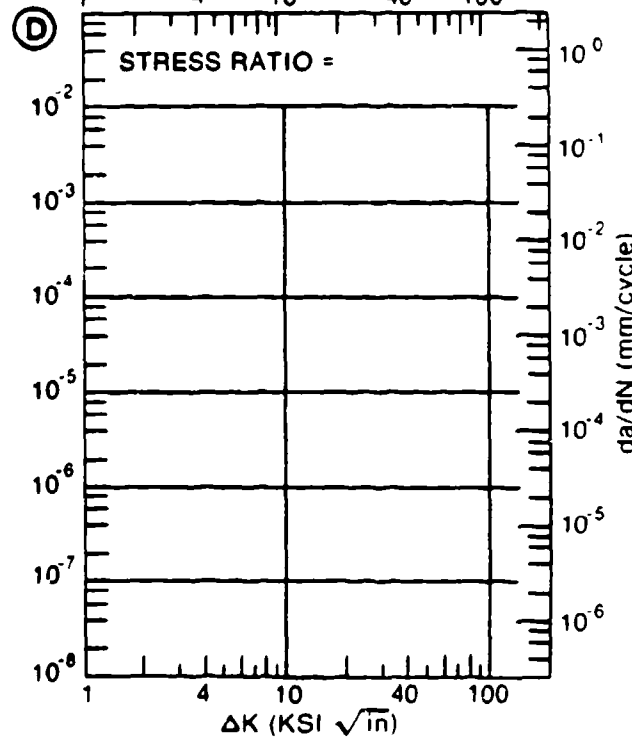
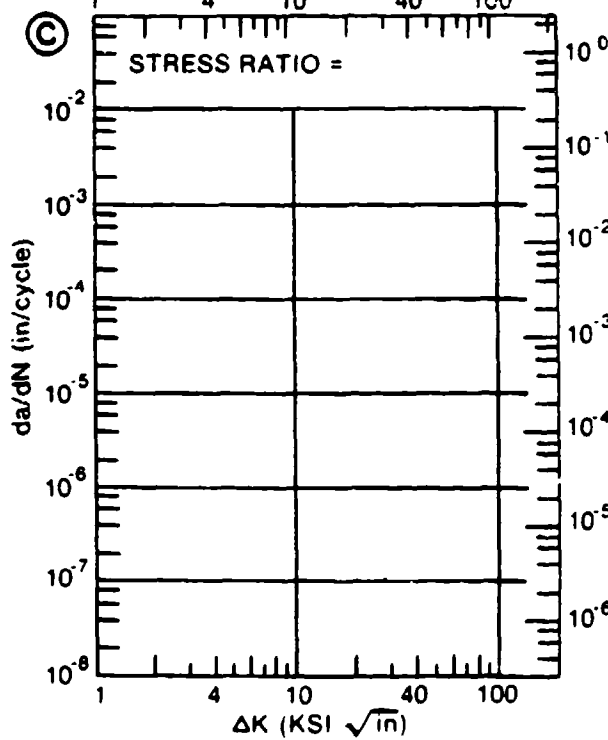
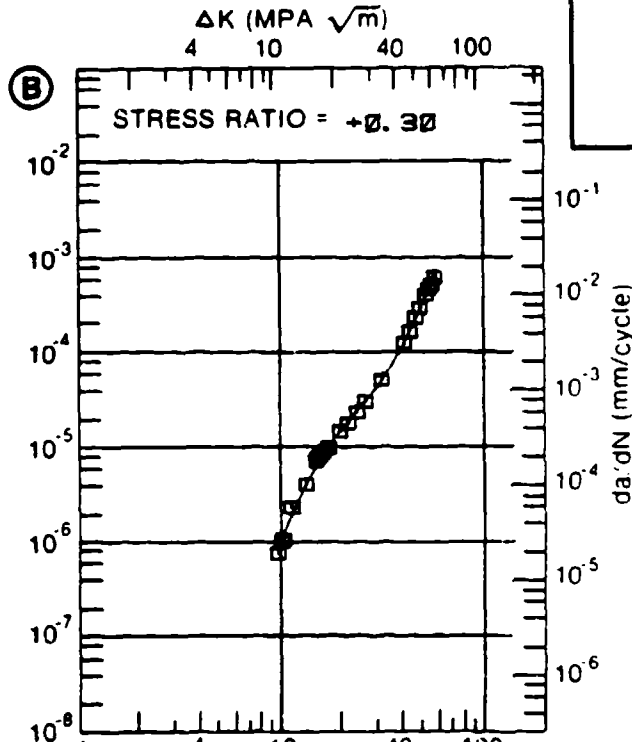
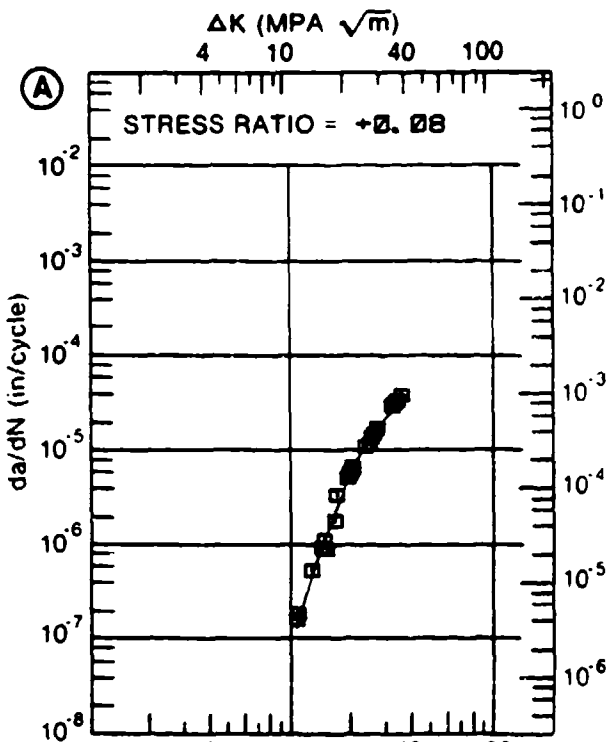


Figure 4.11.3.103

TABLE 4.11.3.104

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.104 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: RA

TI-6AL-4V

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	E= R. T. L. H. A.	E= R. T. J. P. 4		
DELTA K MIN	A: 9.37 : .349			
	B: 12.53 :	.933		
	C:			
	D:			
	10.00 :	.388		
	13.00 :	.844	.812	
	16.00 :	2.04	1.38	
	20.00 :	5.78	5.54	
	25.00 :	15.9	14.2	
	30.00 :	34.1	26.6	
	35.00 :	60.1		
	40.00 :	91.3		
	50.00 :	166.		
DELTA K MAX	A: 58.69 : 341.			
	B: 32.23 :	34.8		
	C:			
	D:			
ROOT MEAN SQUARE PERCENT ERROR	25.76	17.89		

LIFE	0.0-0.5		
PREDICTION	0.5-0.8		
RATIO	0.8-1.25	2	1
SUMMARY	1.25-2.0		
(NP/NA)	>2.0		

CONDITION/HT: RA
 FORM: 4.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 121.0 KSI
 ULT. STRENGTH: 132.0 KSI
 SPECIMEN THK: 0.950- 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 88579

TITAN.
 ALLOY

TI-6AL-
 4V

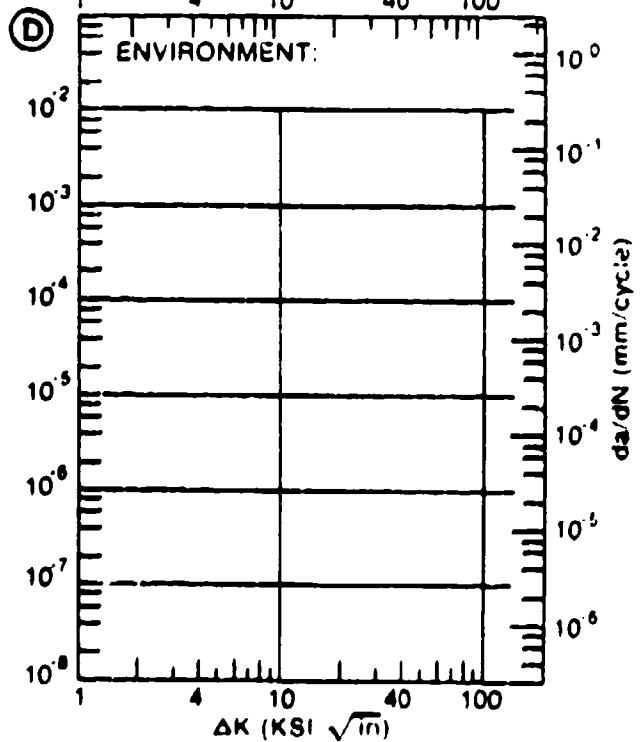
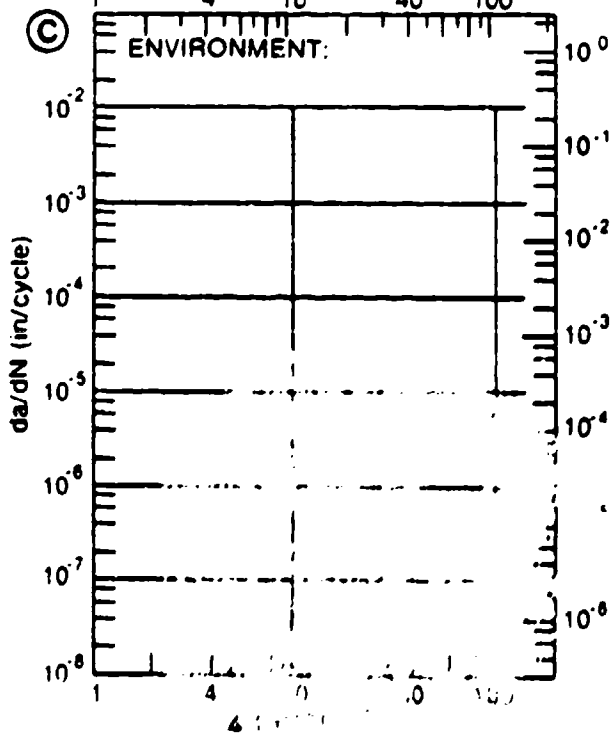
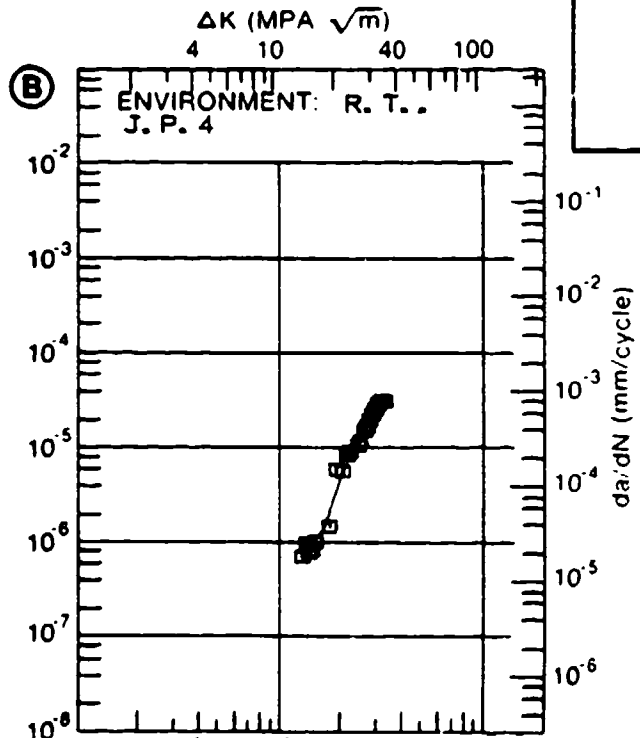
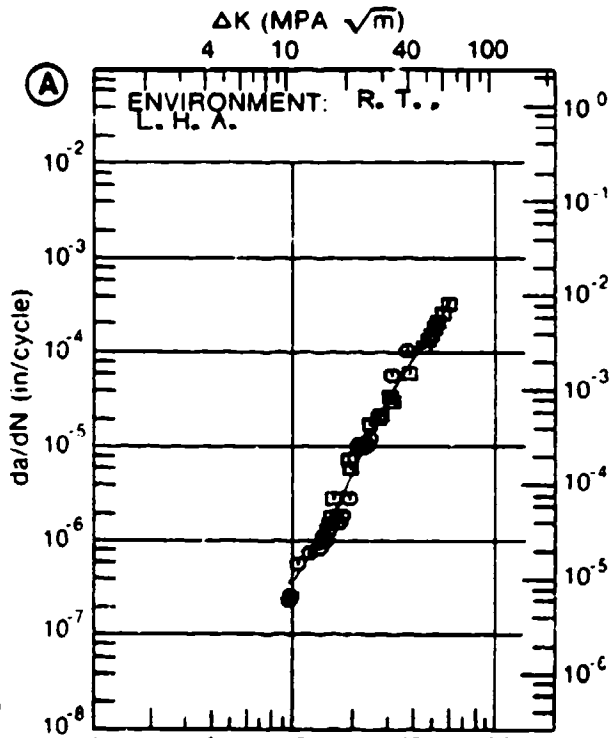


Figure 4.11.3.104

TABLE 4.11.3.105

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.105 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: RA					
ENVIRONMENT: R. T. J. H. A.					
DELTA K (KBI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.50		
DELTA K A:	12.73	.837			
DELTA K B:	9.49		2.14		
MIN C:					
D:					
	10.00		2.68		
	13.00	.920	6.78		
	16.00	2.53	11.9		
	20.00	7.65	19.8		
	25.00	19.1	32.7		
	30.00	32.8	51.6		
	35.00	48.1	71.3		
	40.00	67.2			
	50.00	135.			
	60.00	327.			
DELTA K A:	68.69	885.			
DELTA K B:	37.30		101.		
MAX C:					
D:					
ROOT MEAN SQUARE PERCENT ERROR		13.63	7.38		
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 2.0	1	1		

CONDITION/HT: RA
 FORM: 4.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 8.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 119.0- 128.0 KSI
 ULT. STRENGTH: 127.0- 136.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 88579

TITAN.
 ALLOY

TI-6AL-
 4V

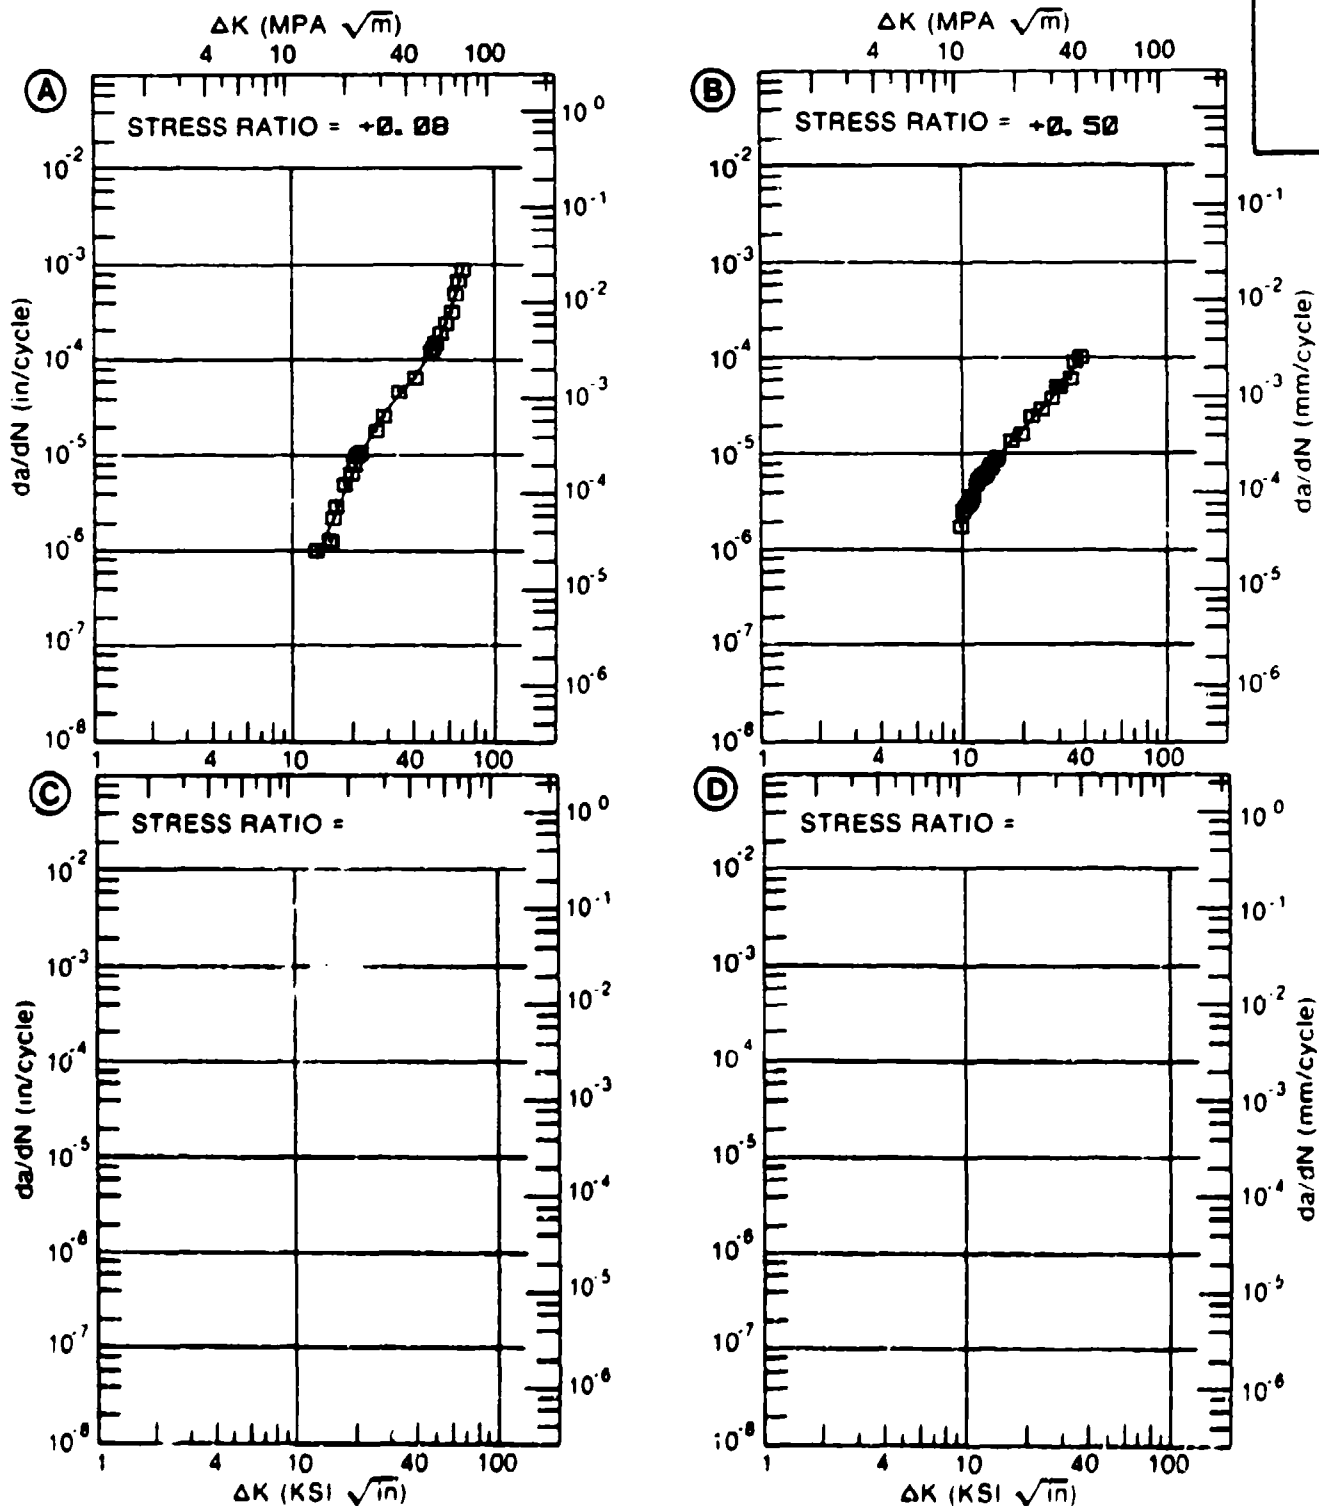


Figure 4.11.3.105

TABLE 4.11.3.106

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.106 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: RA
ENVIRONMENT: R. T. , S. T. W.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.50			
DELTA K MIN	A: 7.69	1.88			
	B:				
	C:				
	D:				
	8.00	1.81			
	9.00	2.18			
	10.00	3.39			
	13.00	14.7			
	16.00	33.8			
	20.00	61.3			
25.00	103.				
30.00	171.				
35.00	277.				
40.00	426.				
DELTA K MAX	A: 40.43	440.			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 15.31
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: RA
 FORM: 4.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 128.0 KSI
 ULT. STRENGTH: 138.0 KSI
 SPECIMEN THK: 0.880"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 98579

TITAN.
 ALLOY

TI-6AL-
 4V

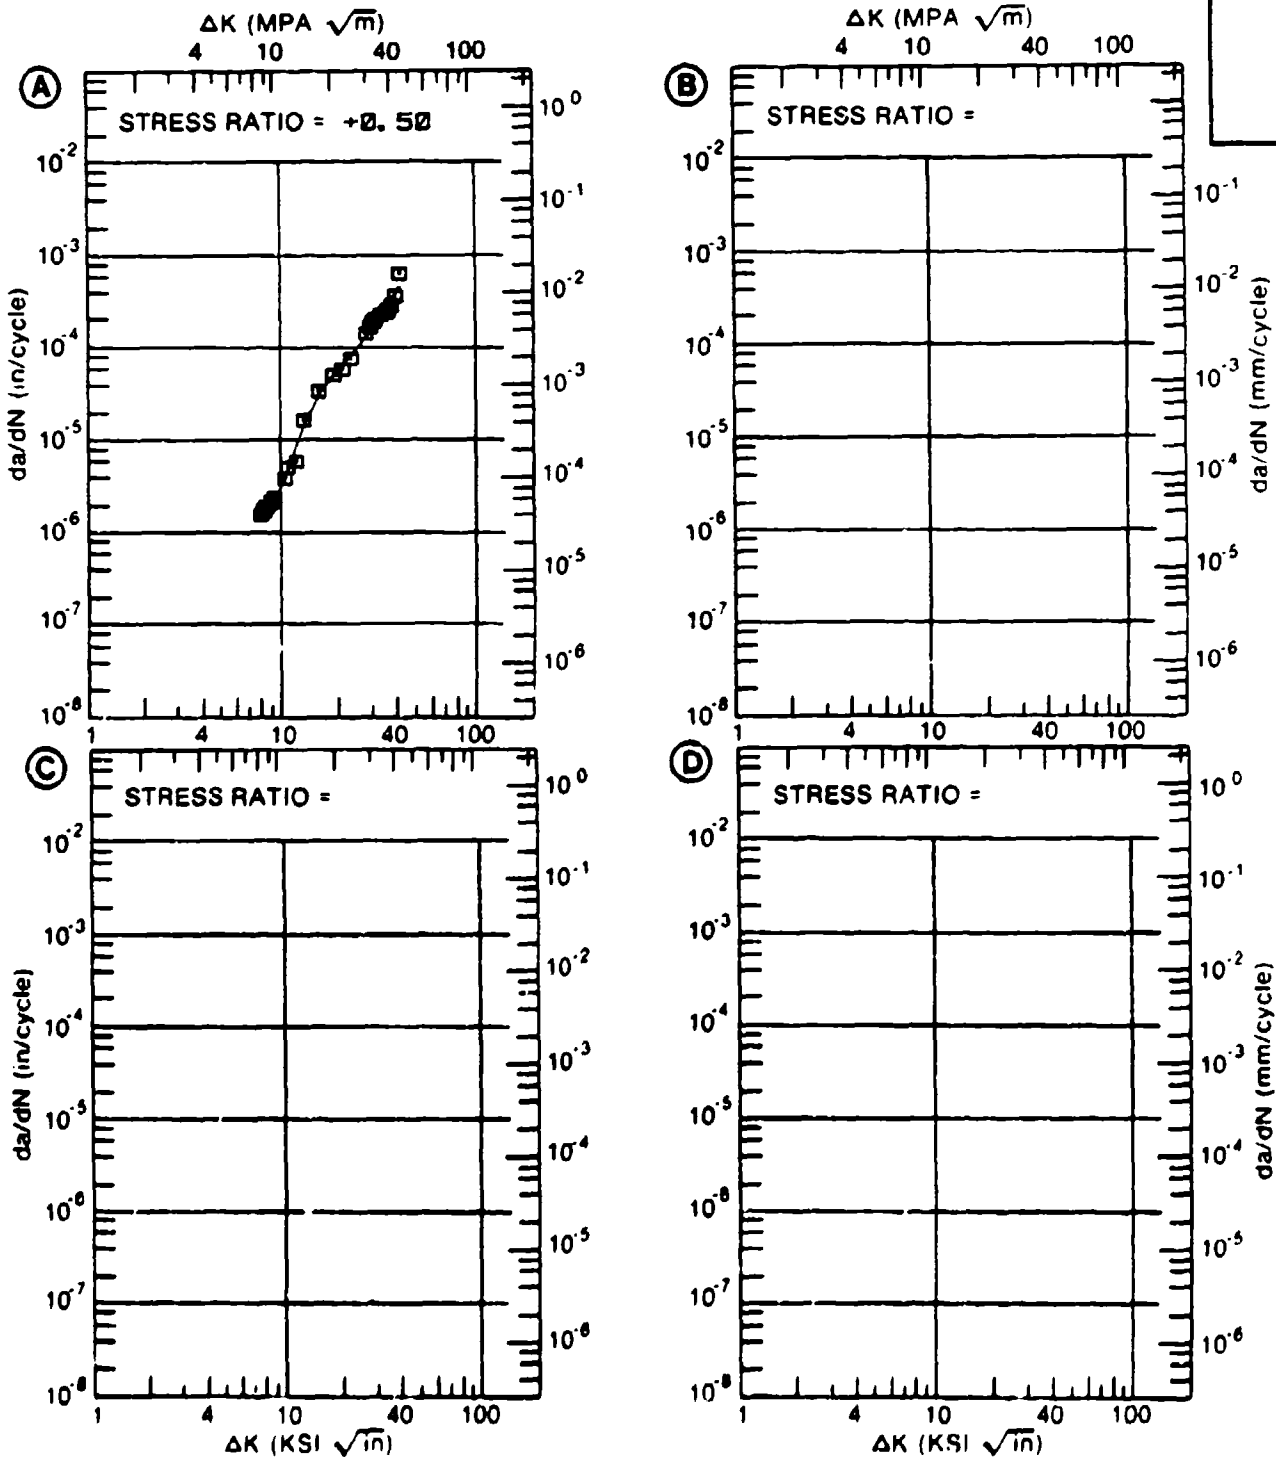


Figure 4.11.3.106

TABLE 4.11.3.107

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.10 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: RA

TI-6AL-4V

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. S. T. W. SP. THK. =. 77"		E= R. T. S. T. W. SP. THK. =1. 04"	
DELTA K	A: 9.95	.707			
MIN	B: 8.02		.186		
	C:				
	D:				
	9.00		.398		
	10.00	.694	.742		
	13.00	1.60	2.75		
	16.00	5.77	6.48		
	20.00	14.0	14.9		
	25.00	29.9	33.5		
	30.00	51.9			
	35.00	79.6			
	40.00	112.			
	50.00	192.			
DELTA K	A: 58.05	270.			
MAX	B: 28.61		56.2		
	C:				
	D:				
ROOT MEAN SQUARE		10.30	25.37		
PERCENT ERROR					
LIFE	0.0-0.9				
PREDICTION	0.5-0.9				
RATIO	0.9-1.25	1			
SUMMARY	1.25-2.0		1		
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM: 4.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 119.0- 128.0 KSI
 ULT. STRENGTH: 127.0- 136.0 KSI
 SPECIMEN THK:
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 88579

TITAN.
 ALLOY

TI-6AL-
 4V

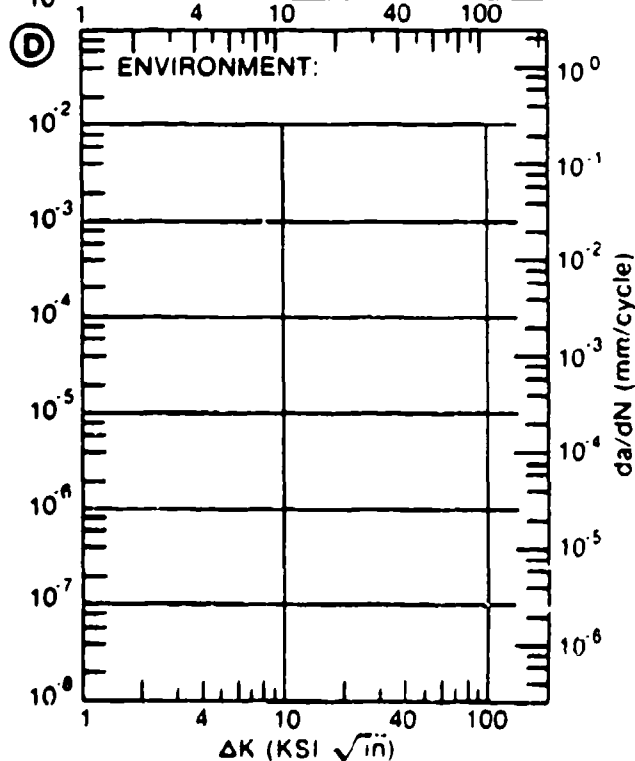
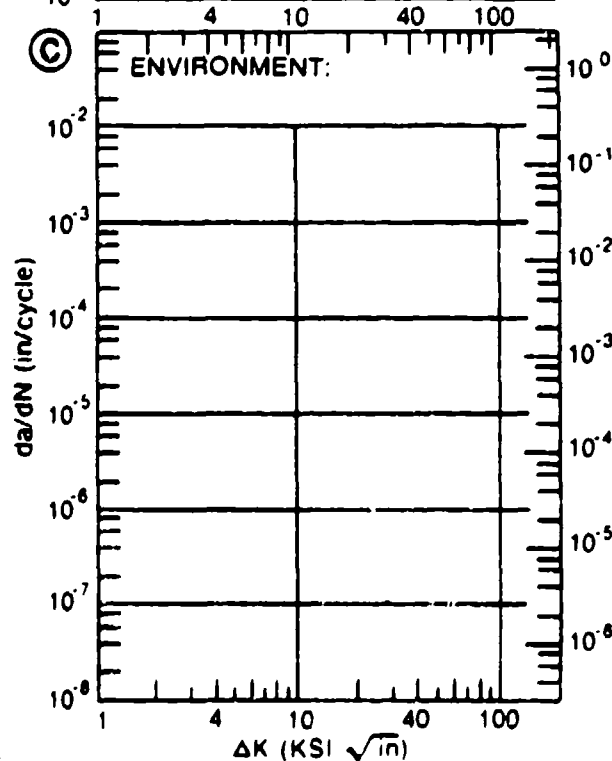
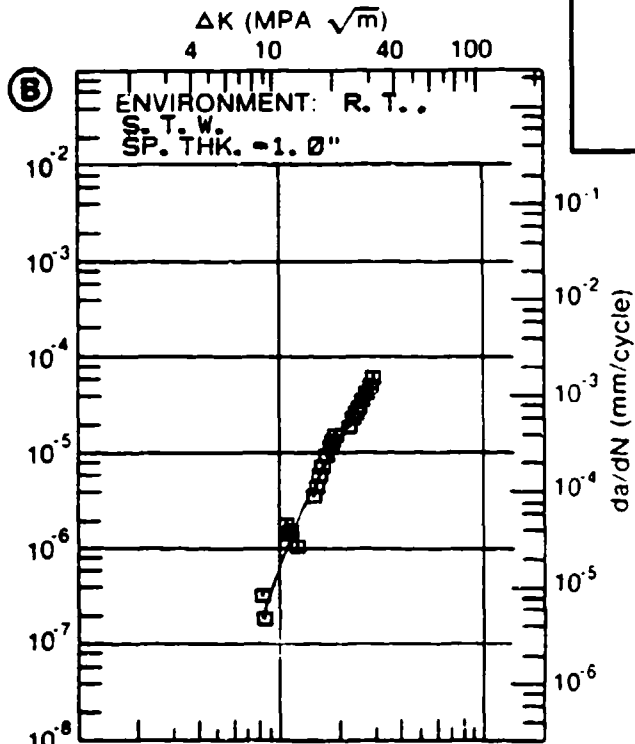
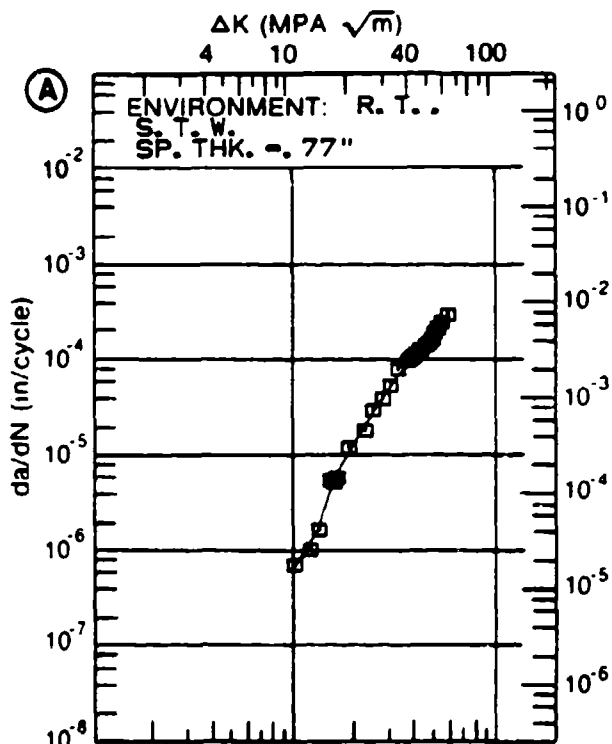


Figure 4.11.3.107

TABLE 4.11.3.108

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.108 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: STOA

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T.			
		L. H. A.			
DELTA K	A: 11.82	9.43			
MIN	B:				
	C:				
	D:				
	13.00	9.10			
	16.00	20.2			
DELTA K	A: 18.56	37.1			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 10.90
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: ST0A
 FORM: 0.02" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.30
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 140.0 KSI
 ULT. STRENGTH: 150.0 KSI
 SPECIMEN THK: 0.491"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 85837

TITAN.
 ALLOY

TI-6AL-
 4V

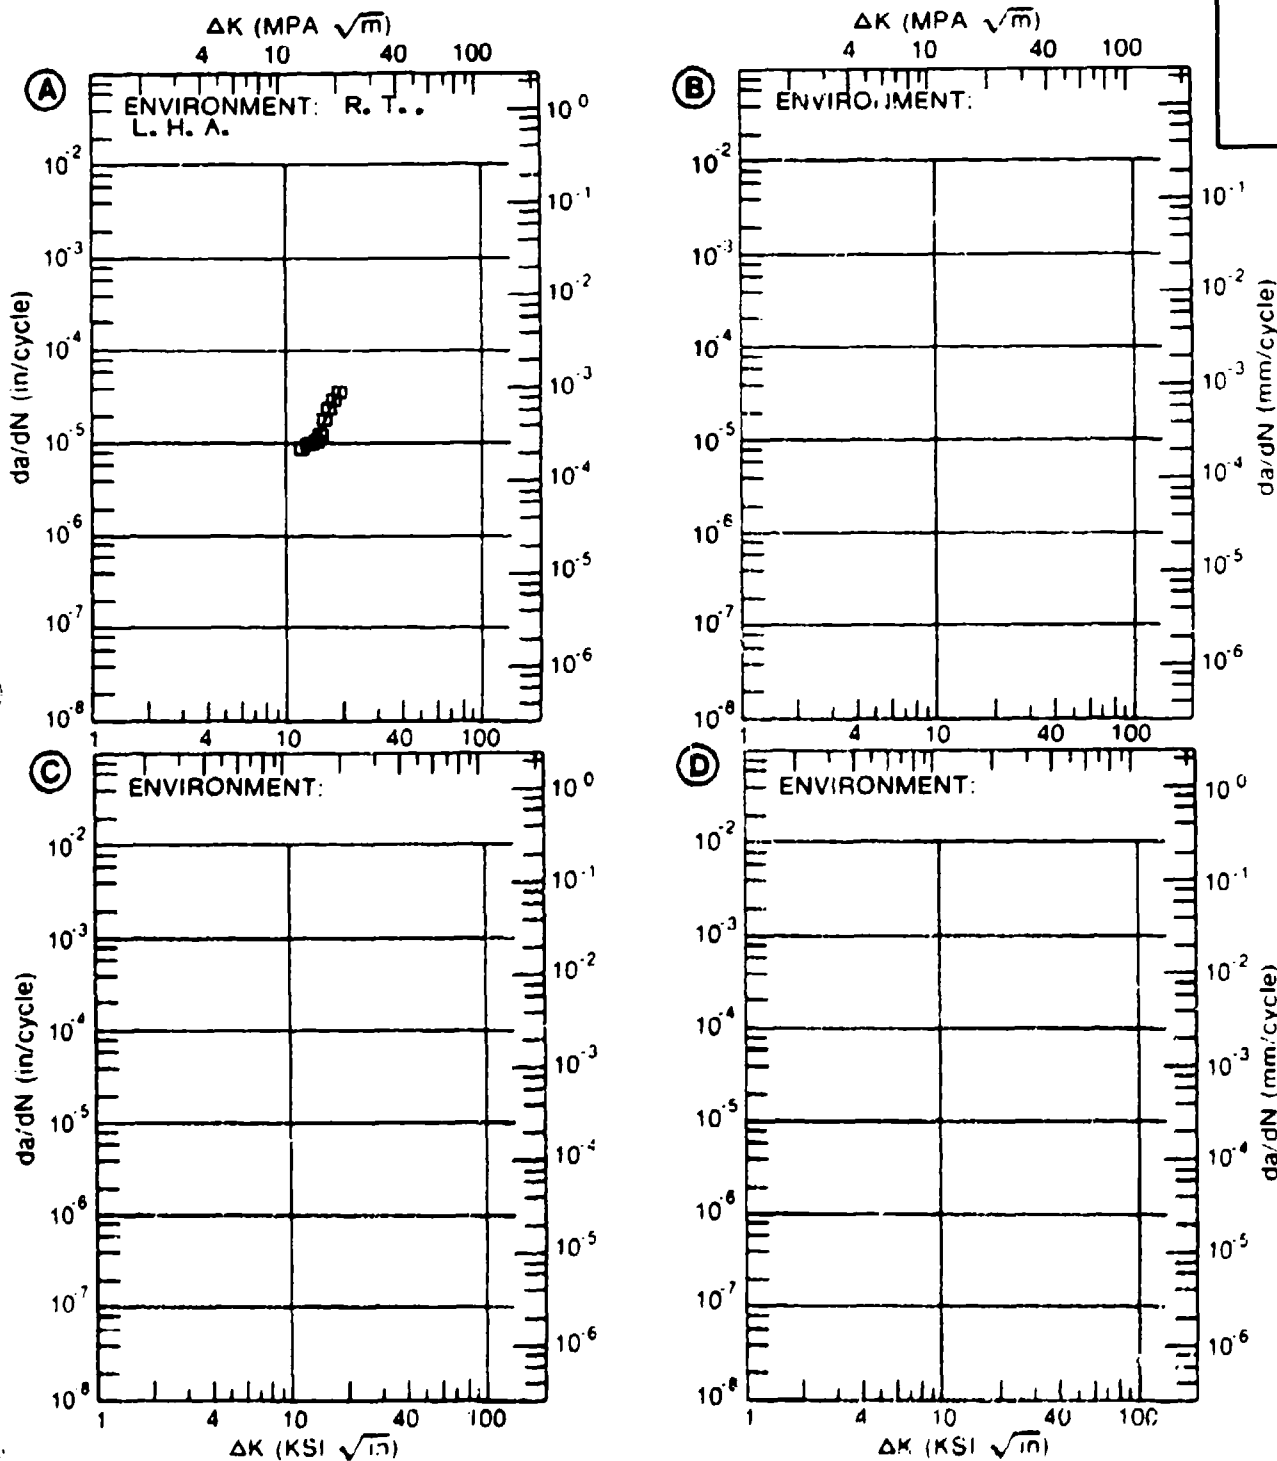


Figure 4.11.3.108

TABLE 4.11.3.109

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.8.109 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: STRESS RELIEVED E. B. WELDMENT (WELD ZONE)

DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E= R. T. DIST. WATER		
DELTA K MIN	A: 15.48	2.20			
	B: 25.76		5.22		
	C:				
	D:				
	16.00	4.77			
	20.00	10.1			
	25.00	24.6			
	30.00	63.5	19.2		
	35.00	175.	78.6		
	40.00	1080.	273.		
	50.00		2053.		
	60.00		9009.		
DELTA K MAX	A: 40.52	1462.			
	B: 68.14		21786.		
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		39.26	111.76		

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: STRESS RELIEVED E. B. WELDMENT (WELD ZONE)
 FORM: 1.00" TH WELDMENT
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 0.10- 10.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: 89144

TITAN.
 ALLOY

TI-6AL-
 4V

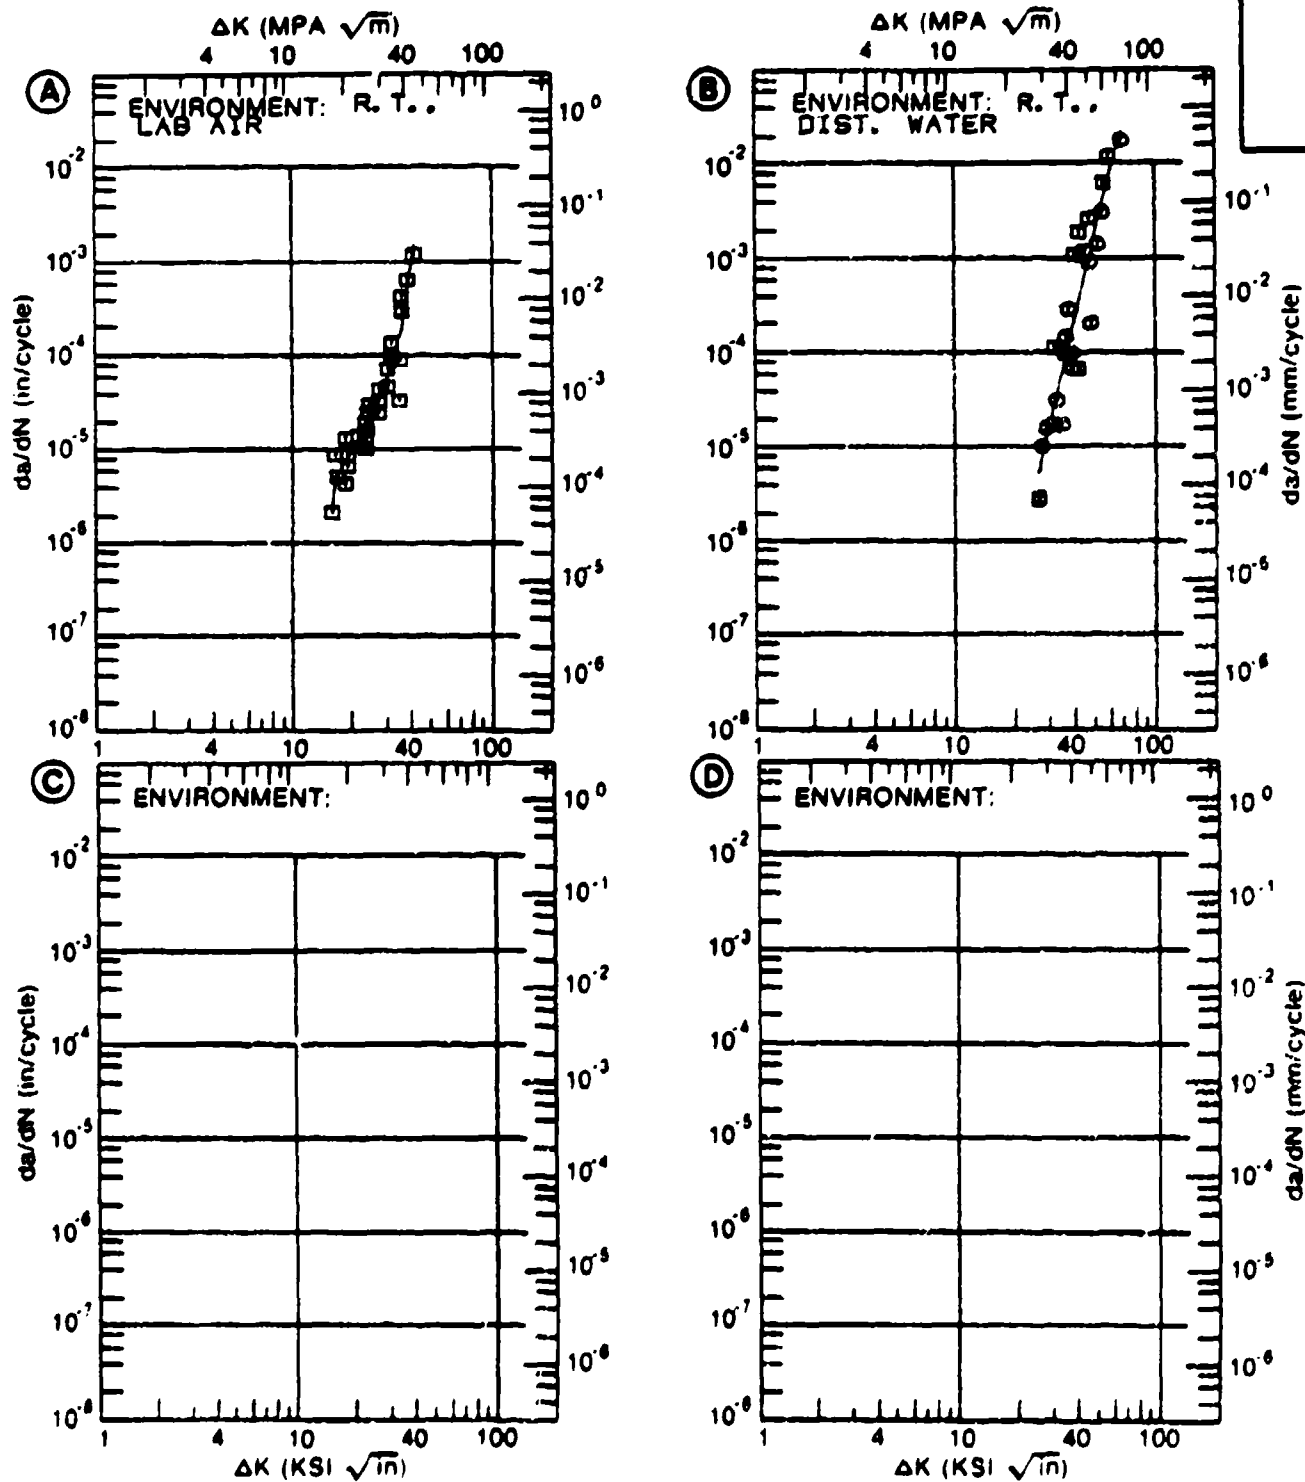


Figure 4.11.3.109

TABLE 4.11.3.110

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.110 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: STRESS RELIEVED E. B. WELDMENT (WELD ZONE)

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN./CYCLE)			
	A	B	C	D
	E= R.T. 3.5% NaCl	E=+ 175F 3.5% NaCl		
DELTA K MIN	A: 21.95 B: 28.50 C: D:	17.8	31.1	
	25.00 30.00 35.00 40.00 50.00	120. 854. 2746. 5987. 18134.	53.6 179. 895.	
DELTA K MAX	A: 51.09 B: 46.69 C: D:	20210.	8328.	
ROOT MEAN SQUARE PERCENT ERROR	74.94	39.82		

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: STRESS RELIEVED E. B. WELDMENT (WELD ZONE)
 FORM: 1.00" TH WELDMENT
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 0.10- 10.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: 88144

TITAN.
 ALLOY

TI-6AL-4V

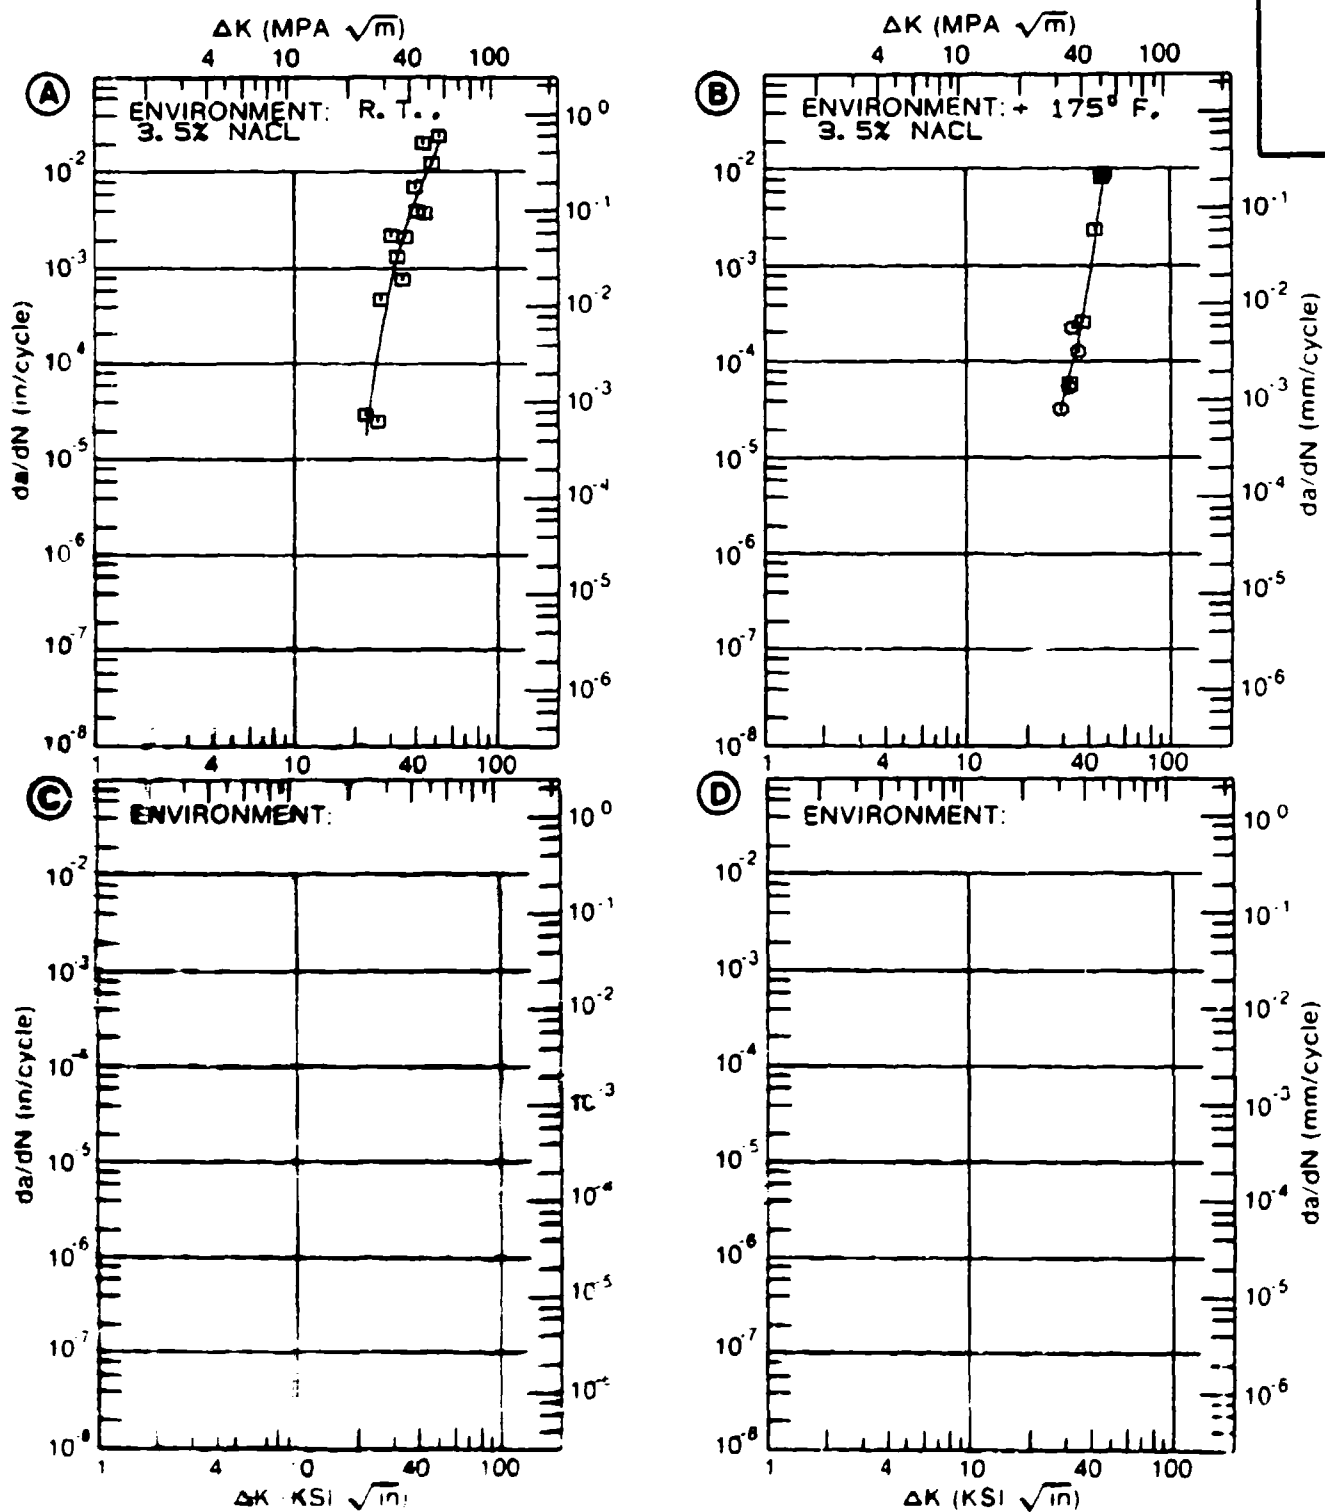


Figure 4.11.3.119

TABLE 4.11.3.111

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.111 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: STRESS RELIEVED E. B. WELDMENT (HEAT
AFFECTED ZONE)

DELTA K (KSI*IN**1/2)	DA/DN (10**6 IN./CYCLE)			
	A	B	C	D
	E= R. T. 3.5% NACL .1-10HZ	E=+ 175F 3.5% NACL 10HZ	E=+ 175F 3.5% NACL .1HZ	
DELTA K MIN	A: 19.78	14.6		
	20.00	13.9		
	25.00	17.7		
	30.00	84.5		
	35.00	626.		
	40.00	4908.		
DELTA K MAX	A: 49.52	172725.		
ROOT MEAN SQUARE PERCENT ERROR	113.68	0.00	0.00	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0			

CONDITION/HT: STRESS RELIEVED E. B. WELDMENT (HEAT AFFECTED ZONE)
 FORM: 1.00" TH WELDMENT
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY:
 YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: 88144

TITAN.
ALLOY

TI-6AL-4V

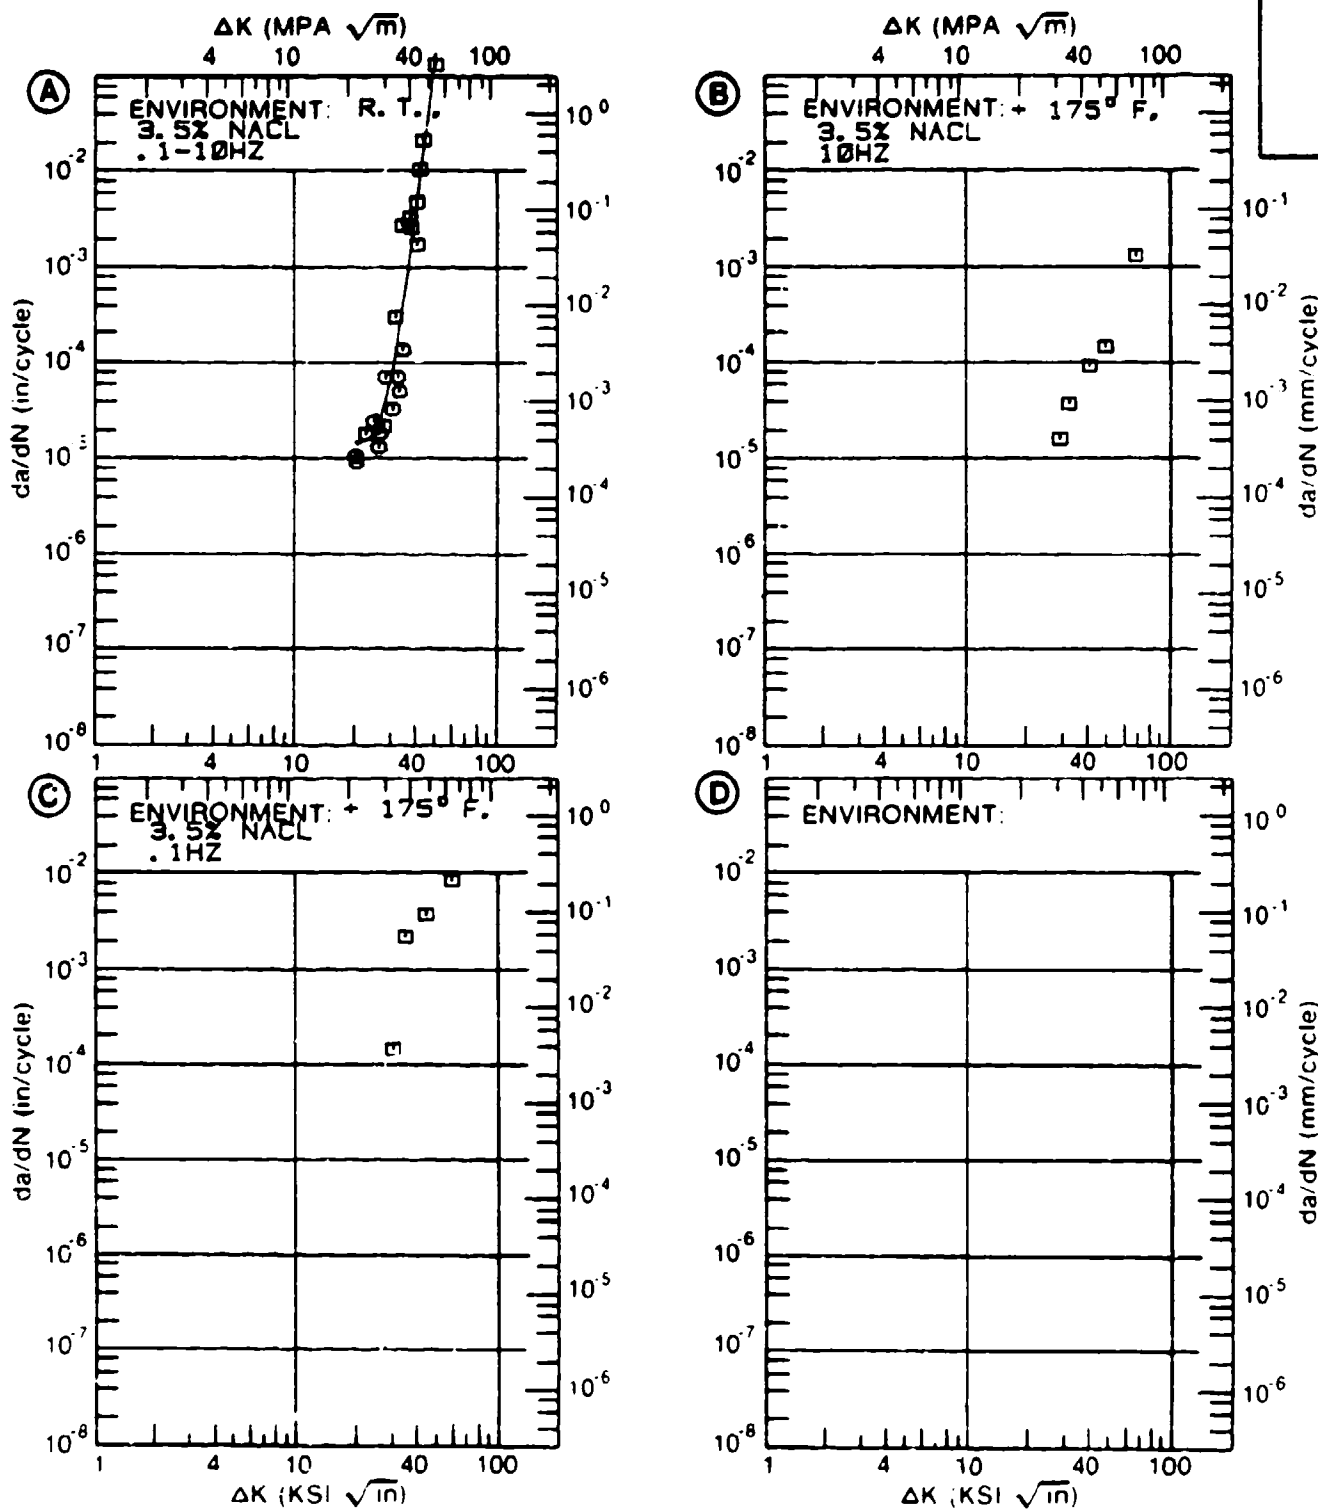


Figure 4.11.3.111

TABLE 4.11.3.112

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.112 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: STRESS RELIEVED E. B. WELDMENT (HEAT
AFFECTED ZONE)

DELTA K (KSI*IN**1/2)	DA/DN (10**6 IN./CYCLE)			
	A	B	C	D
	E= R. T. LAB AIR			
DELTA K MIN	A: 15.64	3.64		
	B: 16.00	4.27		
	C: 20.00	14.2		
	D: 25.00	29.9		
		30.00	47.5	
		35.00	71.9	
		40.00	113.	
		50.00	344.	
DELTA K MAX	A: 52.34	1326.		
	B:			
	C:			
	D:			
ROOT MEAN SQUARE PERCENT ERROR	34.88			

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: STRESS RELIEVED E. B. WELDMENT (HEAT AFFECTED ZONE)
 FORM: 1.00" TH WELDMENT
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 0.10- 10.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: 00144

TITAN. ALLOY
TI-6AL- 4V

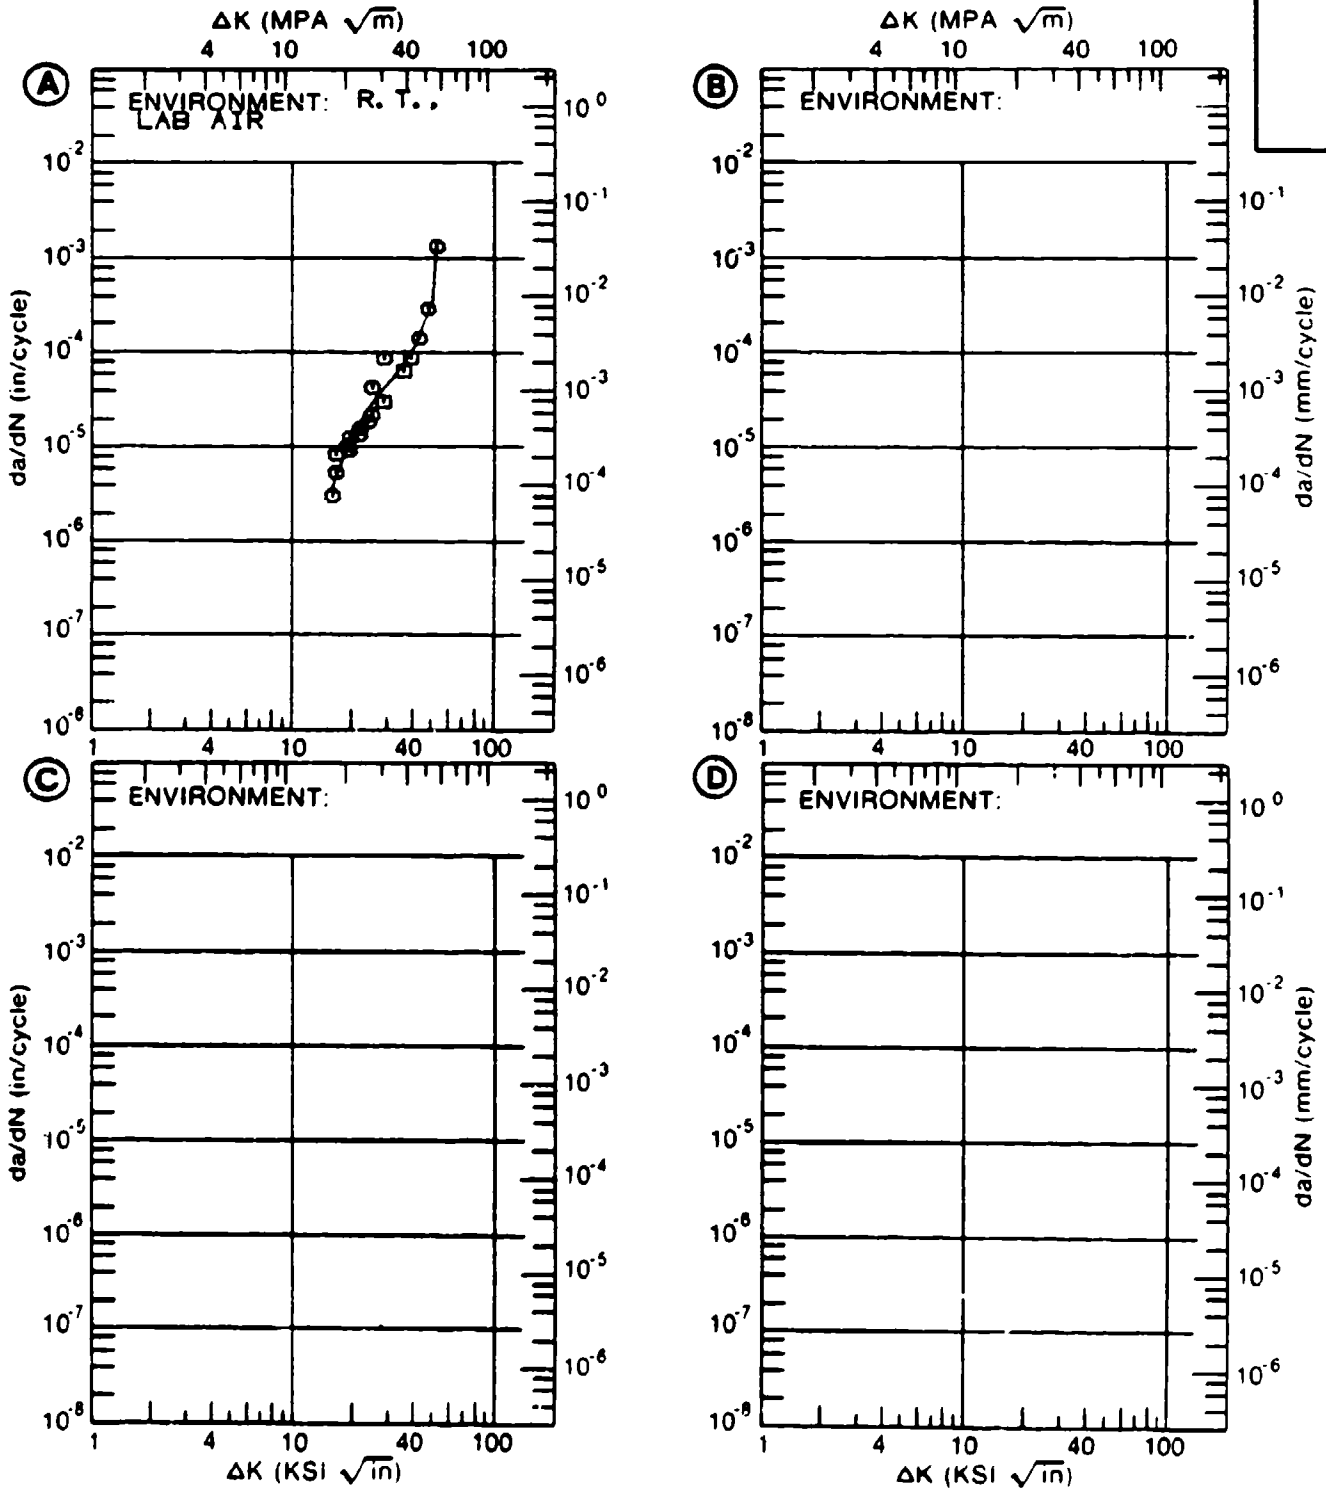


Figure 4.11.3.112

TABLE 4.11.3.113

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.11.3.113 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V

CONDITION: STRESS RELIEVED E. B. WELDMENT (HEAT
AFFECTED ZONE)

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E=- 65F AIR	E=+ 175F AIR	E= R. T. JP-4 FUEL	E=+ 175F DIST. WATER
DELTA K MIN	A:	29.03	59.9		
	B:	16.93		4.81	
	C:	18.23			5.47
	D:	29.99			
		20.00		8.82	9.65
		25.00		15.2	16.8
		30.00	56.6	22.0	22.4
		35.00	143.	32.1	43.5
		40.00	461.	49.8	145.
		50.00		150.	1561.
	60.00		1058.		
DELTA K MAX	A:	43.08	585.		
	B:	61.62		2449.	
	C:	56.28			2318.
	D:	67.44			
					46.8
					46.9
					85.6
					192.
					952.
					3157.
ROOT MEAN SQUARE		54.47	24.73	75.15	53.19
PERCENT ERROR					

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: STRESS RELIEVED E. B. WELDMENT (HEAT AFFECTED ZONE)
 FORM: 1.00" TH WELDMENT YIELD STRENGTH:
 SPECIMEN TYPE: CT ULT. STRENGTH:
 ORIENTATION: T-L SPECIMEN THK: 1.000"
 STRESS RATIO: +0.10 SPECIMEN WIDTH: 2.550"
 FREQUENCY: 0.10- 10.00 HZ REFERENCES: 00144

TITAN.
ALLOY

TI-6AL-
4V

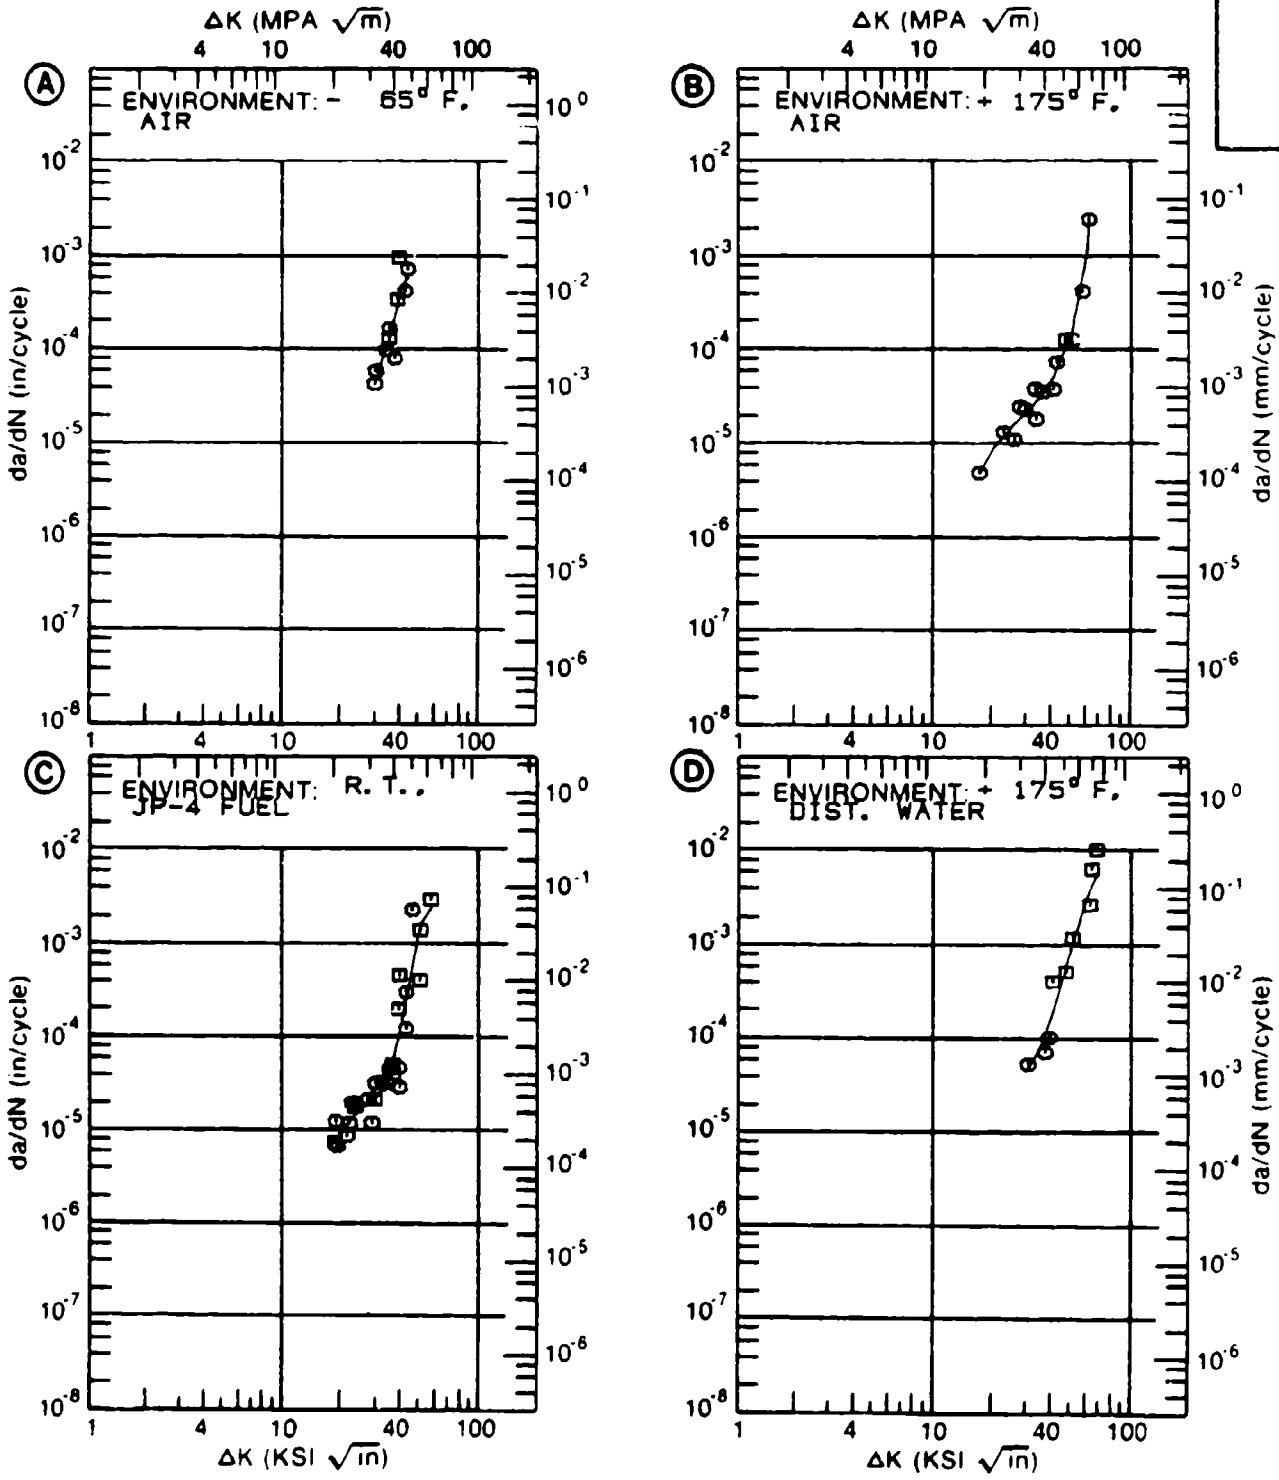


Figure 4.11.3.113

TABLE 4.11.3.114

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.114 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: AS WELDED		E. B. WELDMENT (WELD ZONE)			
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K MIN	A:	16.39	.700		
	B:				
	C:				
	D:				
	20.00	5.94			
	25.00	18.0			
DELTA K MAX	A:	25.00	18.0		
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		37.12			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: AS WELDED
 FORM: 1.00" TH WELDMENT
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

E. B. WELDMENT (WELD ZONE)
 YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: 00144

TITAN. ALLOY
TI-6AL- 4V

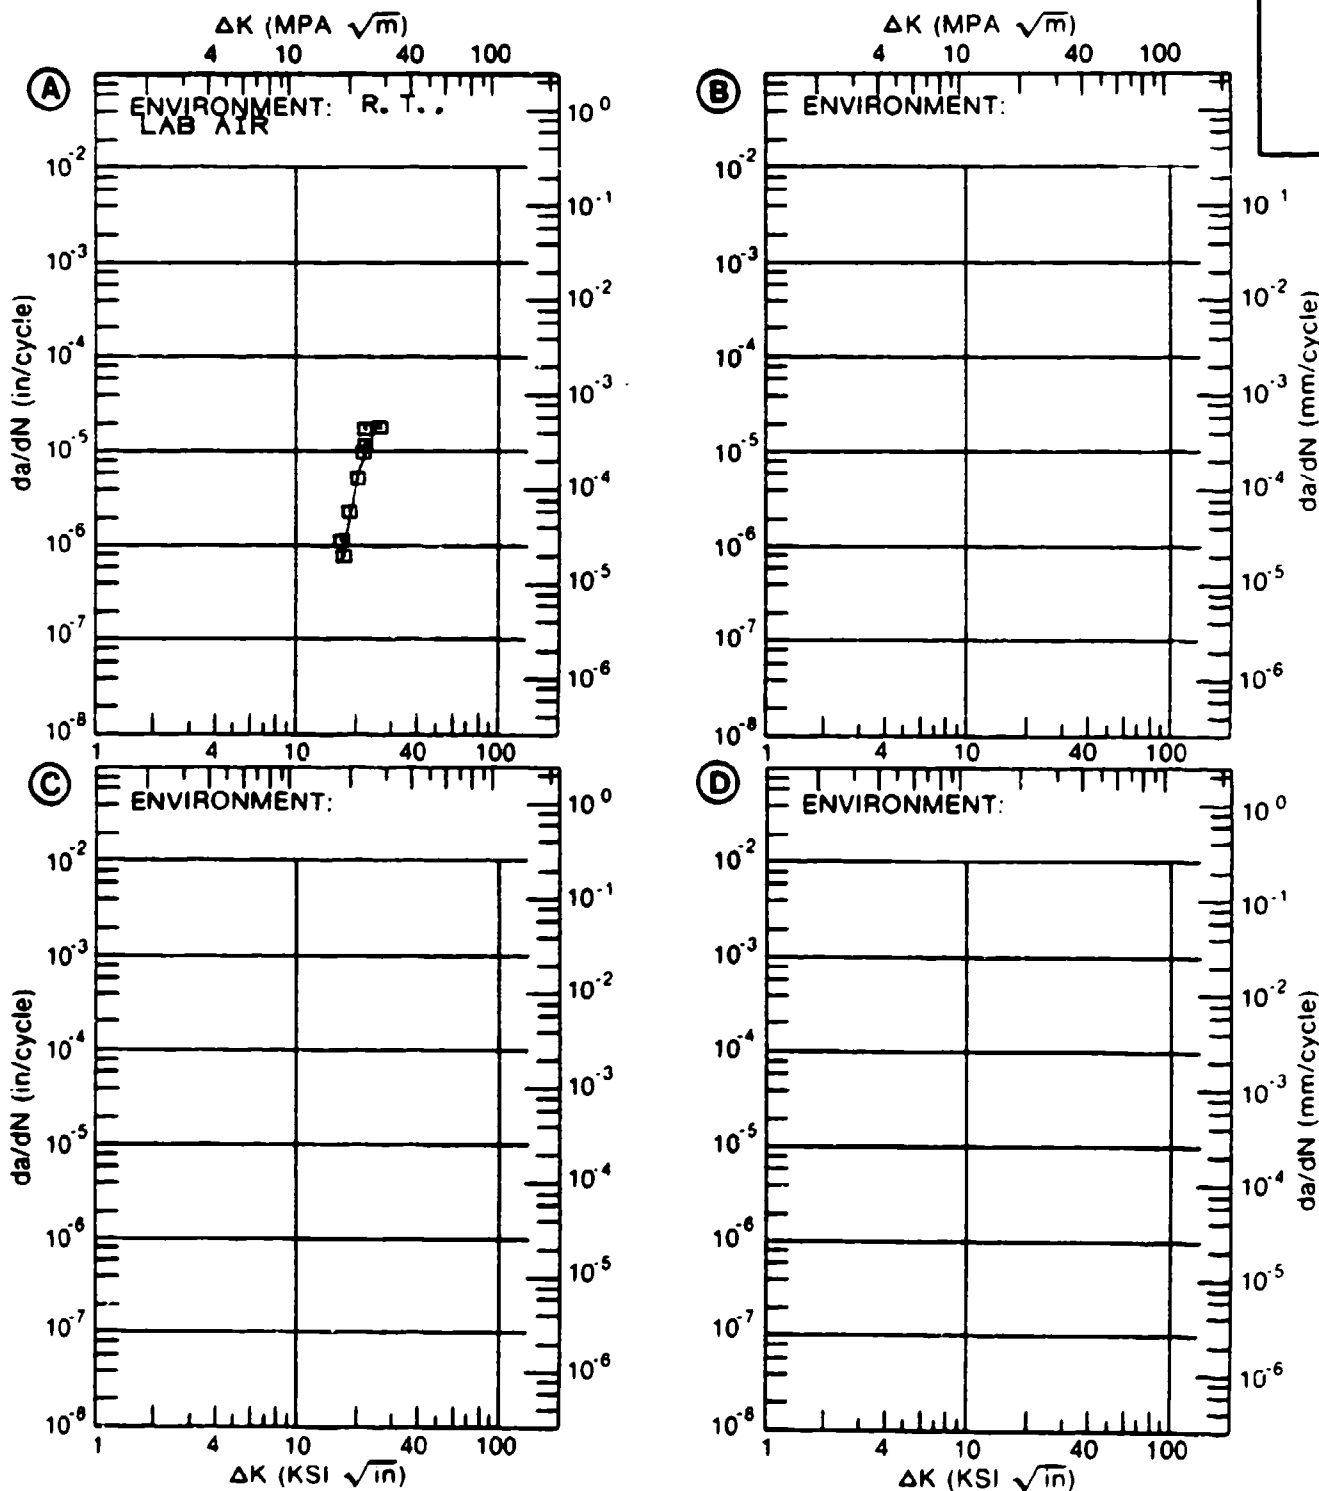


Figure 4.11.3.114

TABLE 4.11.3.115

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.11 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: AS WELDED E. B. WELDMENT (HEAT AFFECTED
ZONE)

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K MIN	A:	15.35	1.98		
	B:				
	C:				
	D:				
		16.00	2.50		
		20.00	6.52		
	25.00	13.2			
	30.00	24.7			
	35.00	50.2			
DELTA K MAX	A:	35.34	52.9		
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 7.47
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: AS WELDED E. B. WELDMENT (HEAT AFFECTED ZONE)
 FORM: 1.00" TH WELDMENT
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: 00144

TITAN.
 ALLOY

TI-6AL-4V

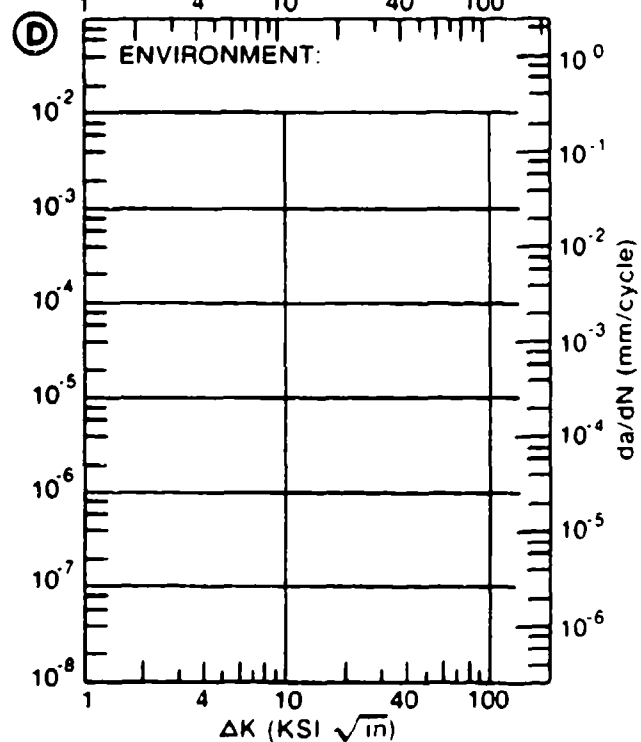
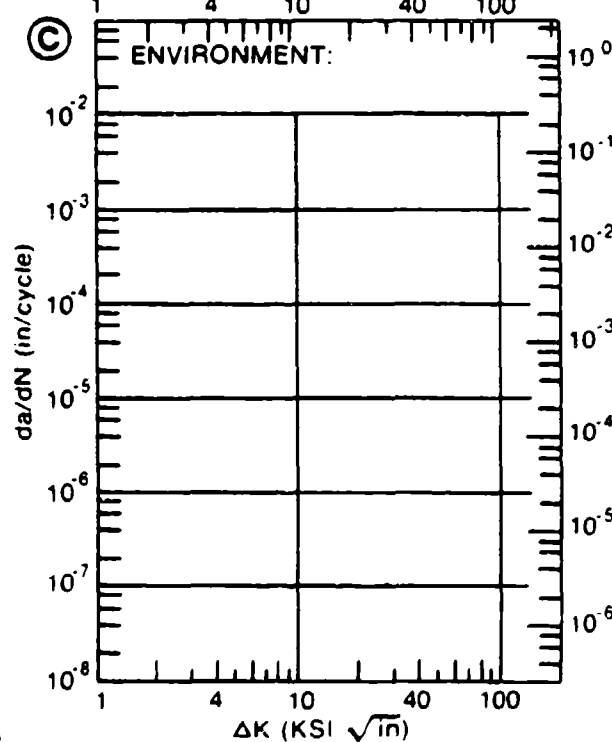
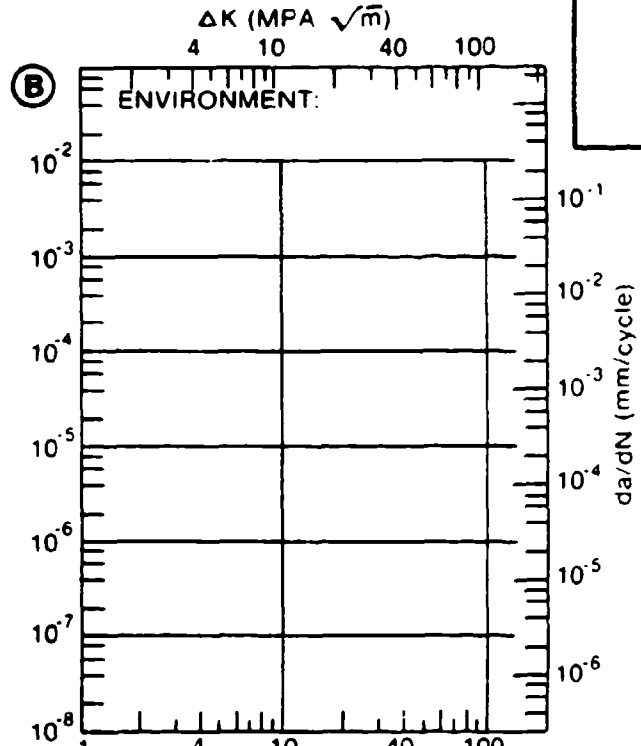
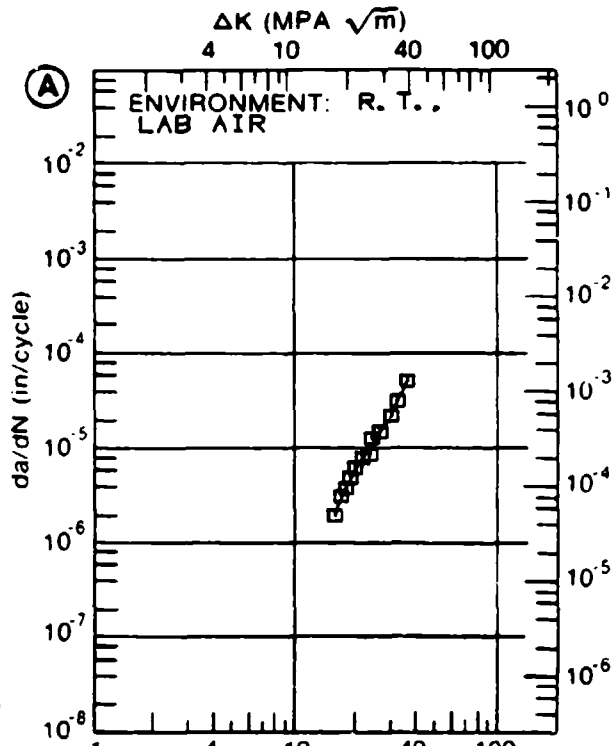


Figure 4.11.3.115

TABLE 4.11.3.116

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.116 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: WELDED & STRESS RELIEVED 1100F 2HRS (HAZ)

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN./CYCLE)			
	A	B	C	D
	E= R. T. L. H. A.	E= R. T. S. T. W.		
DELTA K MIN	A:	B:	C:	D:
200.00				
DELTA K MAX	A:	B:	C:	D:

ROOT MEAN SQUARE 0.00 0.00
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: WELDED & STRESS RELIEVED 1100F 2HRS (HAZ)
 FORM: WELDMENT
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 131.0 KSI
 ULT. STRENGTH: 139.0 KSI
 SPECIMEN THK: 0.088- 0.100"
 SPECIMEN WIDTH: 24.000"
 REFERENCES: 88575

TITAN.
 ALLOY

TI-6AL-
 4V

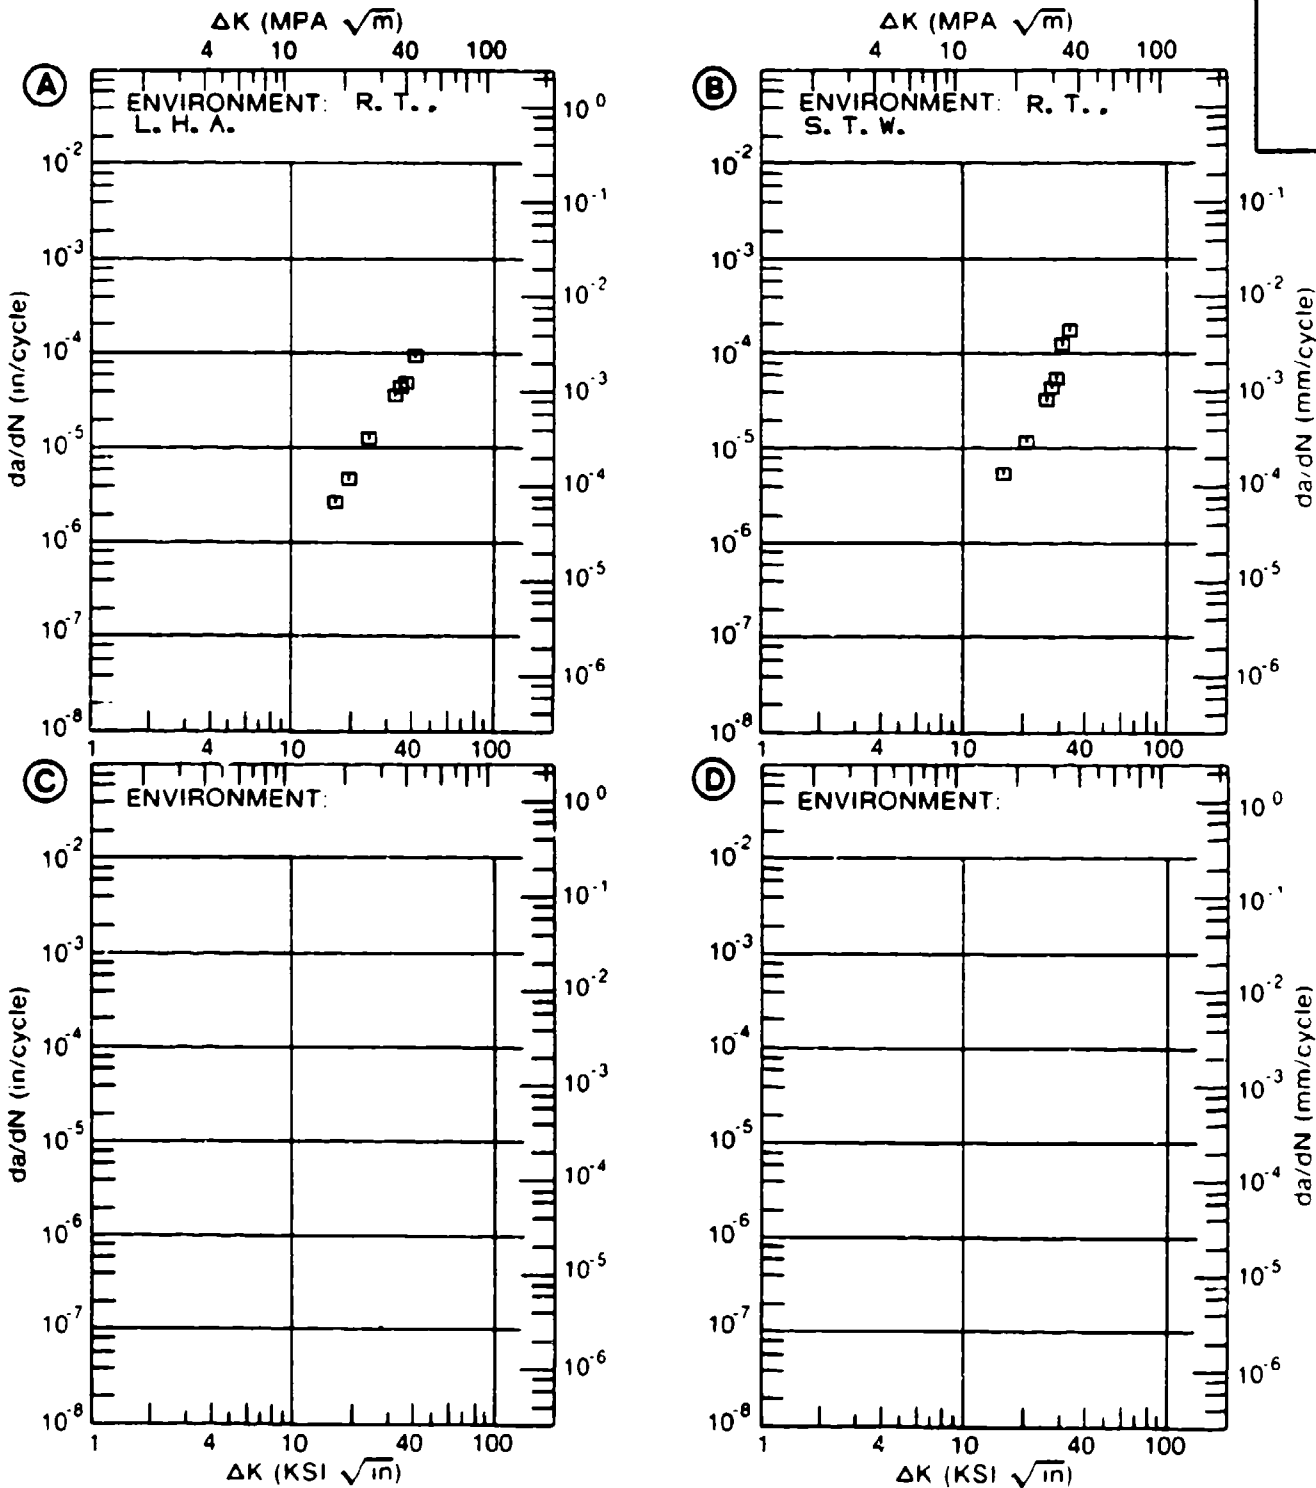


Figure 4.11.3.116

TABLE 4.11.3.117

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.11.3.117 INDICATING EFFECT
OF ENVIRONMENTMATERIAL: TITANIUM TI-6AL-4V
CONDITION: 1550F 4HRS FC, 1000F 4HRS, ARGON COOLED

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. ARGON	E= R. T. ARGON		
DELTA K MIN	A: 9.68	.15			
	B: 10.56		.26		
	C:				
	D:				
	10.00	.195			
	13.00	.886	.854		
	16.00	1.94	1.96		
	20.00	3.81	4.08		
	25.00	7.97	9.01		
	30.00	18.1	21.0		
	35.00	46.8	54.5		
	40.00	137.	158.		
DELTA K MAX	A: 44.83	434.			
	B: 41.26		209.		
	C:				
	D:				
ROOT MEAN SQUARE		29.57	28.88		
PERCENT ERROR					

LIFE 0.0-0.5
 PREDICTION 0.5-0.8
 RATIO 0.8-1.25
 SUMMARY 1.25-2.0
 (NP/NA) >2.0

CONDITION/HT: 1550F 4HRS FC, 1000F 4HRS, ARGON COOLED
 FORM: FORGING
 SPECIMEN TYPE: WOL
 ORIENTATION: R-C
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH: 140.9 KSI
 ULT STRENGTH: 150.1 KSI
 SPECIMEN THK: 0.000"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: UM001

TITAN.
ALLOY

TI-6AL-
4V

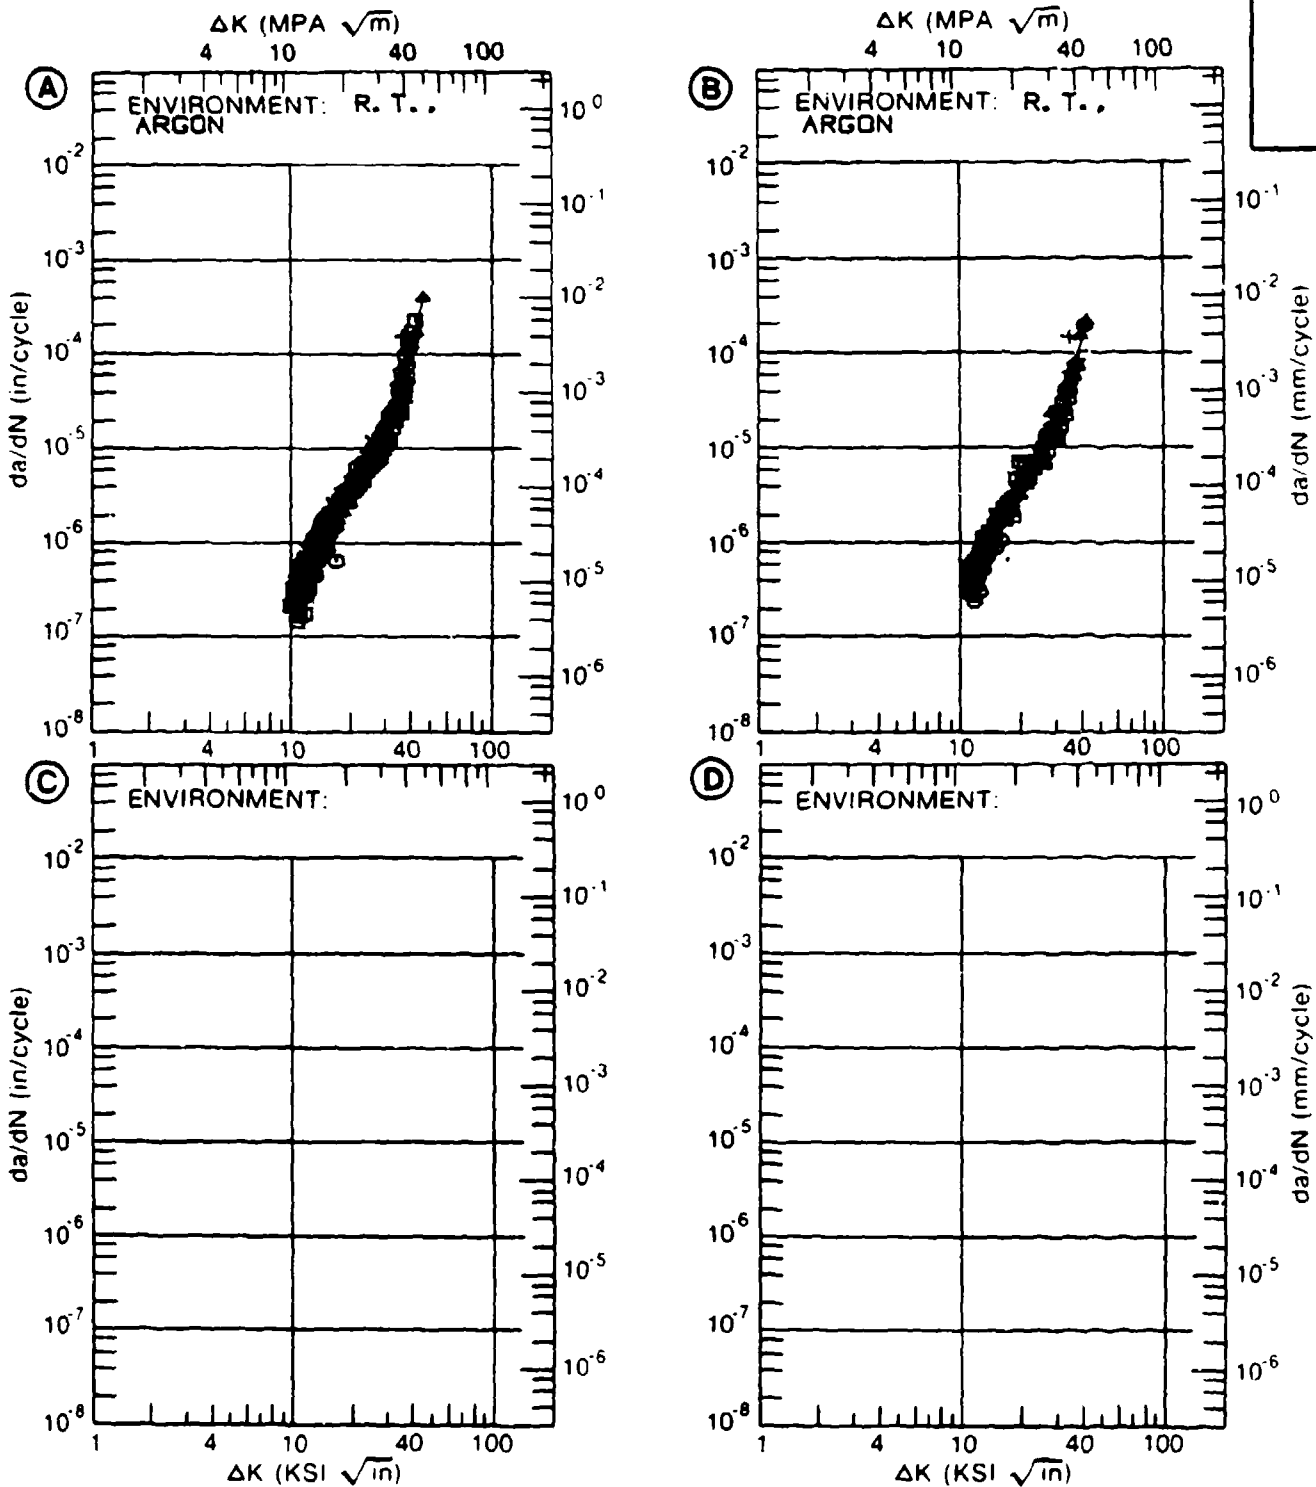


Figure 4.11.3.117

TABLE 4.11.3.118

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.118 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: 1750F 4HRS ARGON COOLED, 1000F 4HRS,
ARGON COOLED

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	E= R. T. ARGON		E= R. T. ARGON	
DELTA K MIN	A: 10.46	.20	B: 10.57	.15
	C: 13.00	.850	D: 16.00	.539
		2.04		1.54
		4.05		4.13
		8.51		10.5
		20.4		23.1
		59.1		48.0
		207.		97.7
DELTA K MAX	A: 42.45	407.	B: 43.64	163.
	C:		D:	
ROOT MEAN SQUARE PERCENT ERROR	31.31		41.13	

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1750F 4HRS ARGON COOLED, 1000F 4HRS, ARGON COOLED
 FORM: FORGING
 SPECIMEN TYPE: WOL
 ORIENTATION: R-C
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH: 135.7 KSI
 ULT. STRENGTH: 144.9 KSI
 SPECIMEN THK: 0.800"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: UM001

TITAN.
ALLOY

TI-6AL-4V

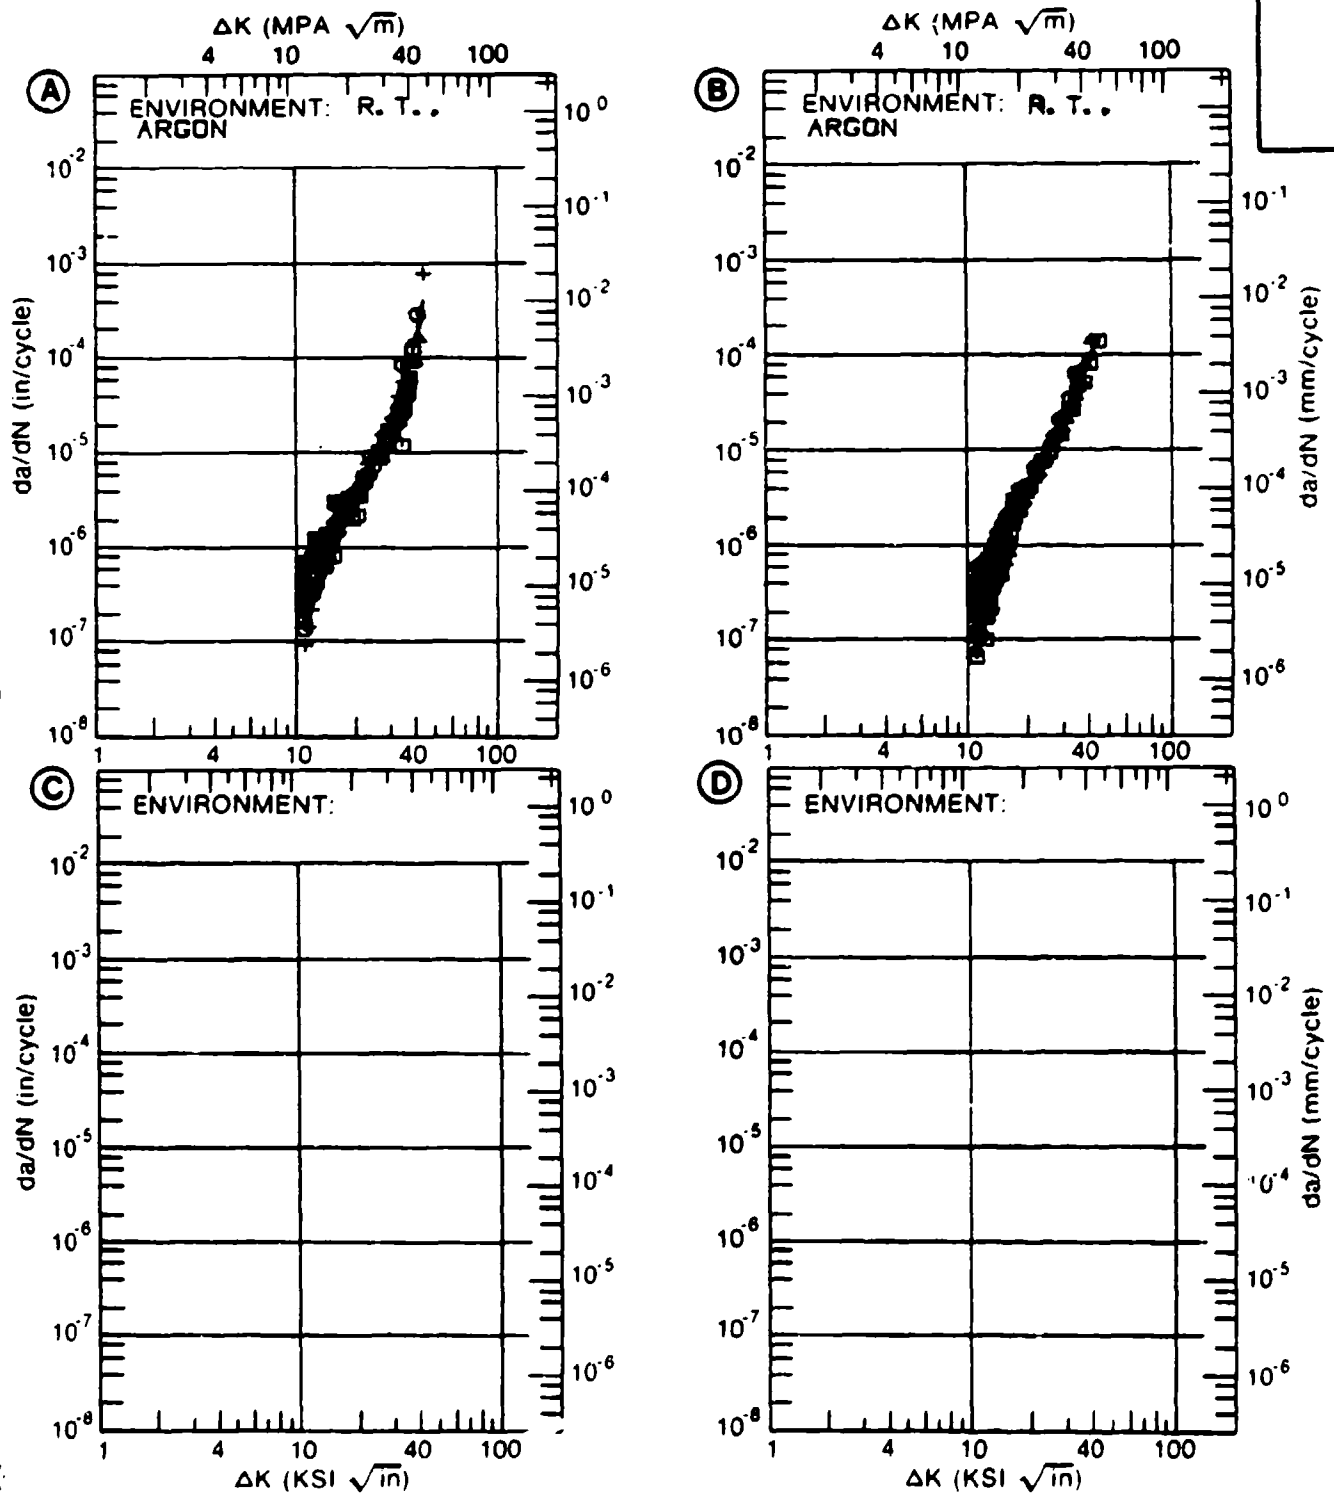


Figure 4.11.3.118

TABLE 4.11.3.119

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.119 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: 1750F 4HRS ARGON COOLED, 1000F 4HRS
ARGON COOLED

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. ARGON			
DELTA K MIN	A:	10.71	.231		
	B:				
	C:				
	D:				
		13.00	.681		
		16.00	1.81		
		20.00	4.61		
	25.00	11.7			
	30.00	27.1			
	35.00	60.7			
	40.00	229.			
DELTA K MAX	A:	40.42	360.		
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 23.92
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1750F 4HRS ARGON COOLED, 1000F 4HRS ARGON COOLED
 FORM: FORGING YIELD STRENGTH: 135.7 KSI
 SPECIMEN TYPE: WOL ULT. STRENGTH: 144.9 KSI
 ORIENTATION: C-R SPECIMEN THK: 0.800"
 STRESS RATIO: +0.10 SPECIMEN WIDTH: 2.550"
 FREQUENCY: 10.00 HZ REFERENCES: UM001

TITAN.
 ALLOY
 TI-6AL-
 4V

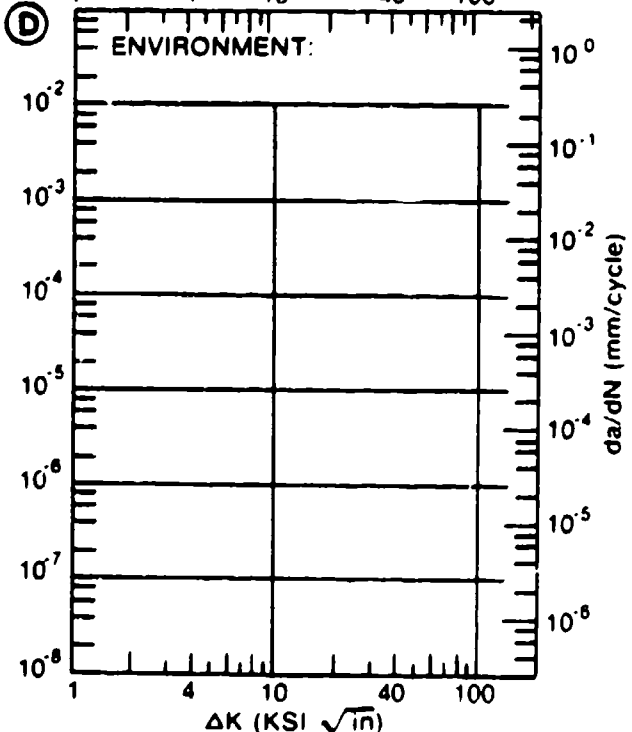
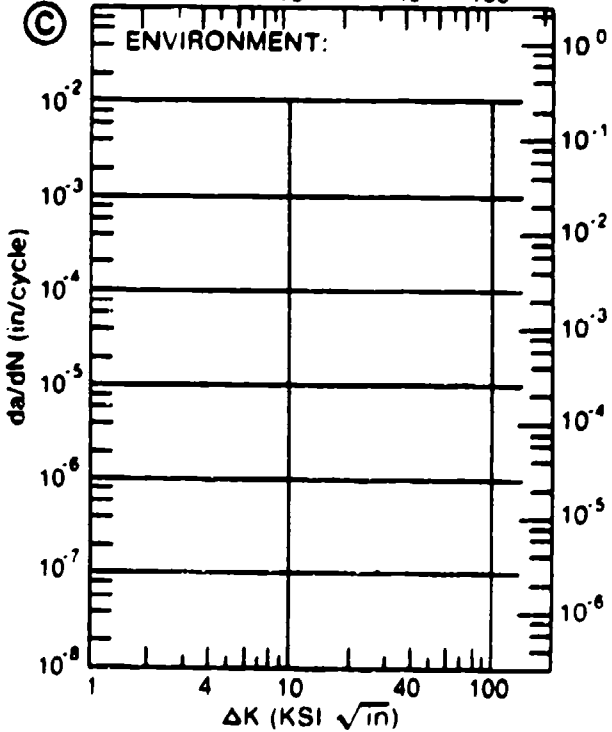
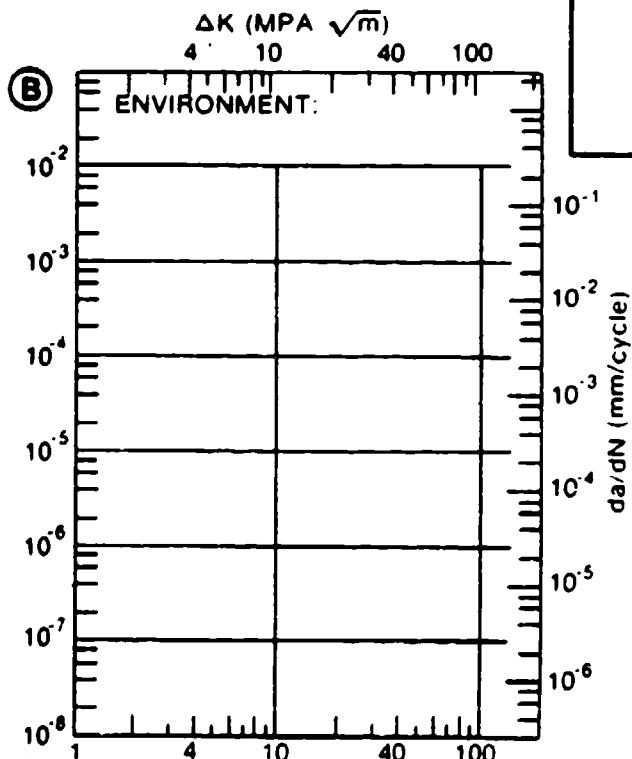
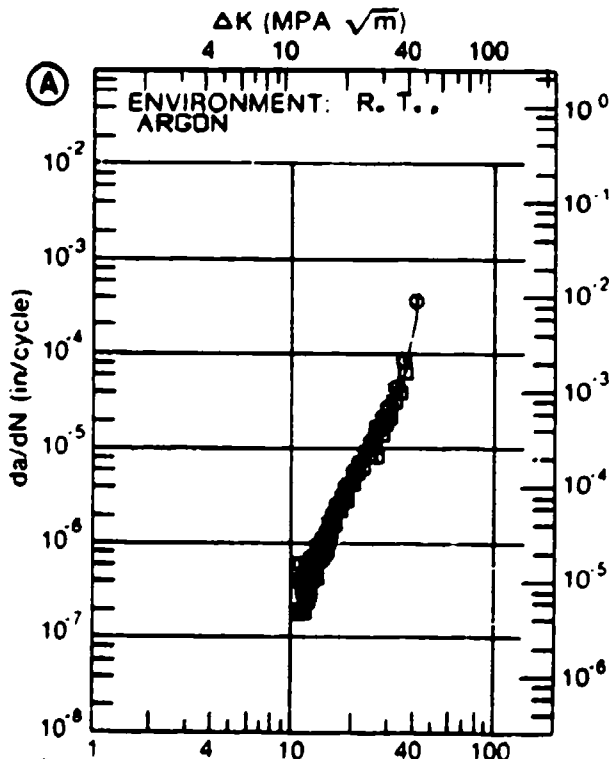


Figure 4.11.3.119

TABLE 4.11.3.120

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.120 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: 1775F 1HR WG, 1675F 1HR WG, 1000F 4HRS
AC, 900F 5HR AC

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN./CYCLE)			
	A	B	C	D
	E= R. T. LAB AIR		E=+ 200F AIR	
DELTA K A: 30.47	37.2			
MIN B: 30.79		48.5		
C:				
D:				
35.00	58.5	96.8		
40.00	83.9	167.		
50.00	152.	356.		
60.00	290.	745.		
70.00	625.	1817.		
80.00	1545.			
DELTA K A: 80.58	1635.			
MAX B: 74.44		2874.		
C:				
D:				
ROOT MEAN SQUARE	7.07	7.10		
PERCENT ERROR				
LIFE	0.0-0.5			
PREDICTION	0.5-0.8		1	
RATIO	0.8-1.25	1		
SUMMARY	1.25-2.0			
(NP/NA)	>2.0			

CONDITION/HT: 1775F 1HR WQ, 1875F 1HR WQ, 1000F 4HRS AC, 900F 5HR AC
 FORM: 0.50" TH DISK
 SPECIMEN TYPE: CCP
 ORIENTATION: C-R
 STRESS RATIO: +0.05
 FREQUENCY: 0.33- 10.00 HZ

YIELD STRENGTH: 120.0 KSI
 ULT. STRENGTH: 130.0 KSI
 SPECIMEN THK: 0.120"
 SPECIMEN WIDTH: 1.980"
 REFERENCES: GE003

TITAN.
ALLOY

TI-6AL-
4V

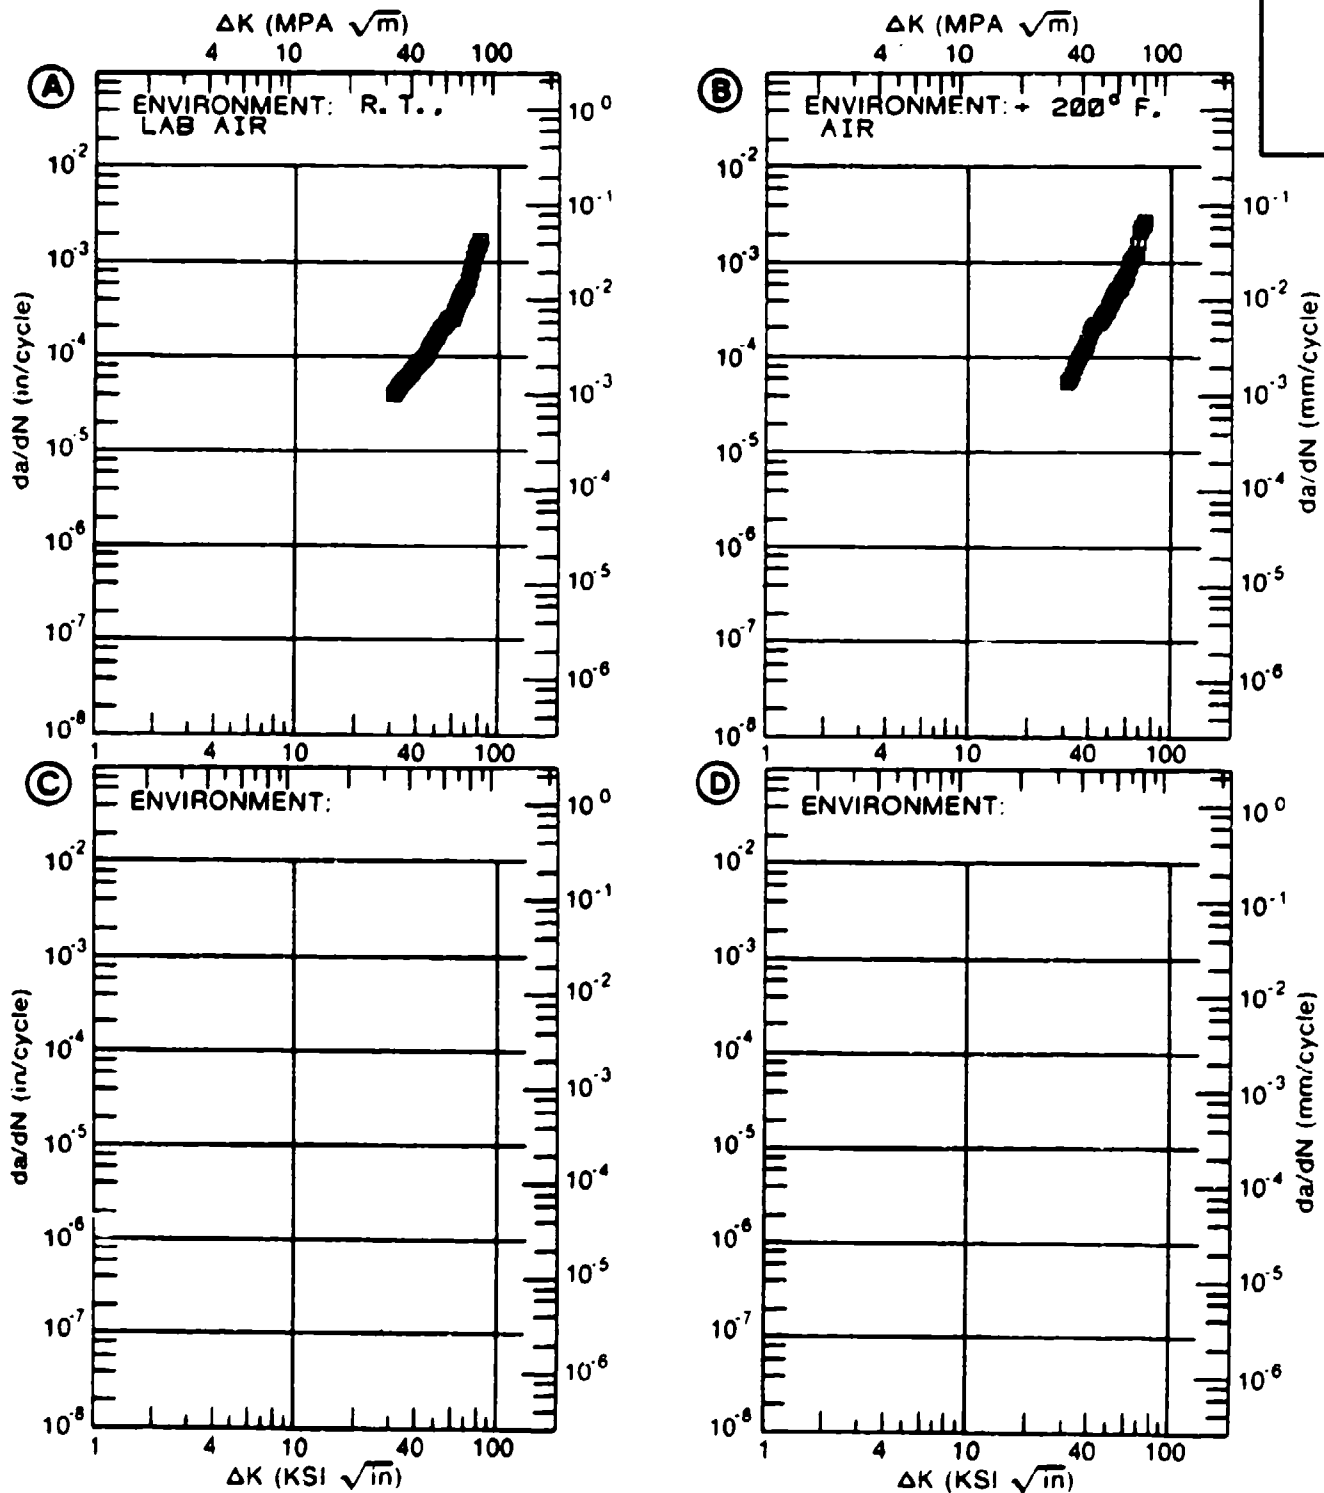


Figure 4.11.3.120

TABLE 4.11.3.121

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.121 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: 1775F 1HR WG, 1675F 1HR WG, 1000F-1200F
2-8HRS AC
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.03	R=+0.25	R=+0.54	
DELTA K	A: 9.85	.788			
MIN	B: 10.87		2.71		
	C: 10.48			3.11	
	D:				
	10.00	.865			
	13.00	3.13	4.91	6.16	
	16.00	6.22	9.51	11.5	
	20.00	11.0	18.9		
	25.00	18.9	37.5		
	30.00	32.1	66.2		
	35.00	57.0			
	40.00	107.			
DELTA K	A: 44.18	191.			
MAX	B: 30.68		71.1		
	C: 19.06			15.7	
	D:				
ROOT MEAN SQUARE		15.97	10.81	14.72	
PERCENT ERROR					

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1775F 1HR WQ, 1675F 1HR WQ, 1000F-1200F 2-8HRS AC
 FORM: 0.94" TH DISK YIELD STRENGTH: 150.0 KSI
 SPECIMEN TYPE: KB BAR ULT. STRENGTH:
 ORIENTATION: C-R SPECIMEN THK: 0.251- 0.252"
 FREQUENCY: 0.33- 0.50 HZ SPECIMEN WIDTH: 0.989- 1.000"
 ENVIRONMENT: R. T., LAB AIR REFERENCES: GE007

TITAN.
ALLOY

TI-6AL-
4V

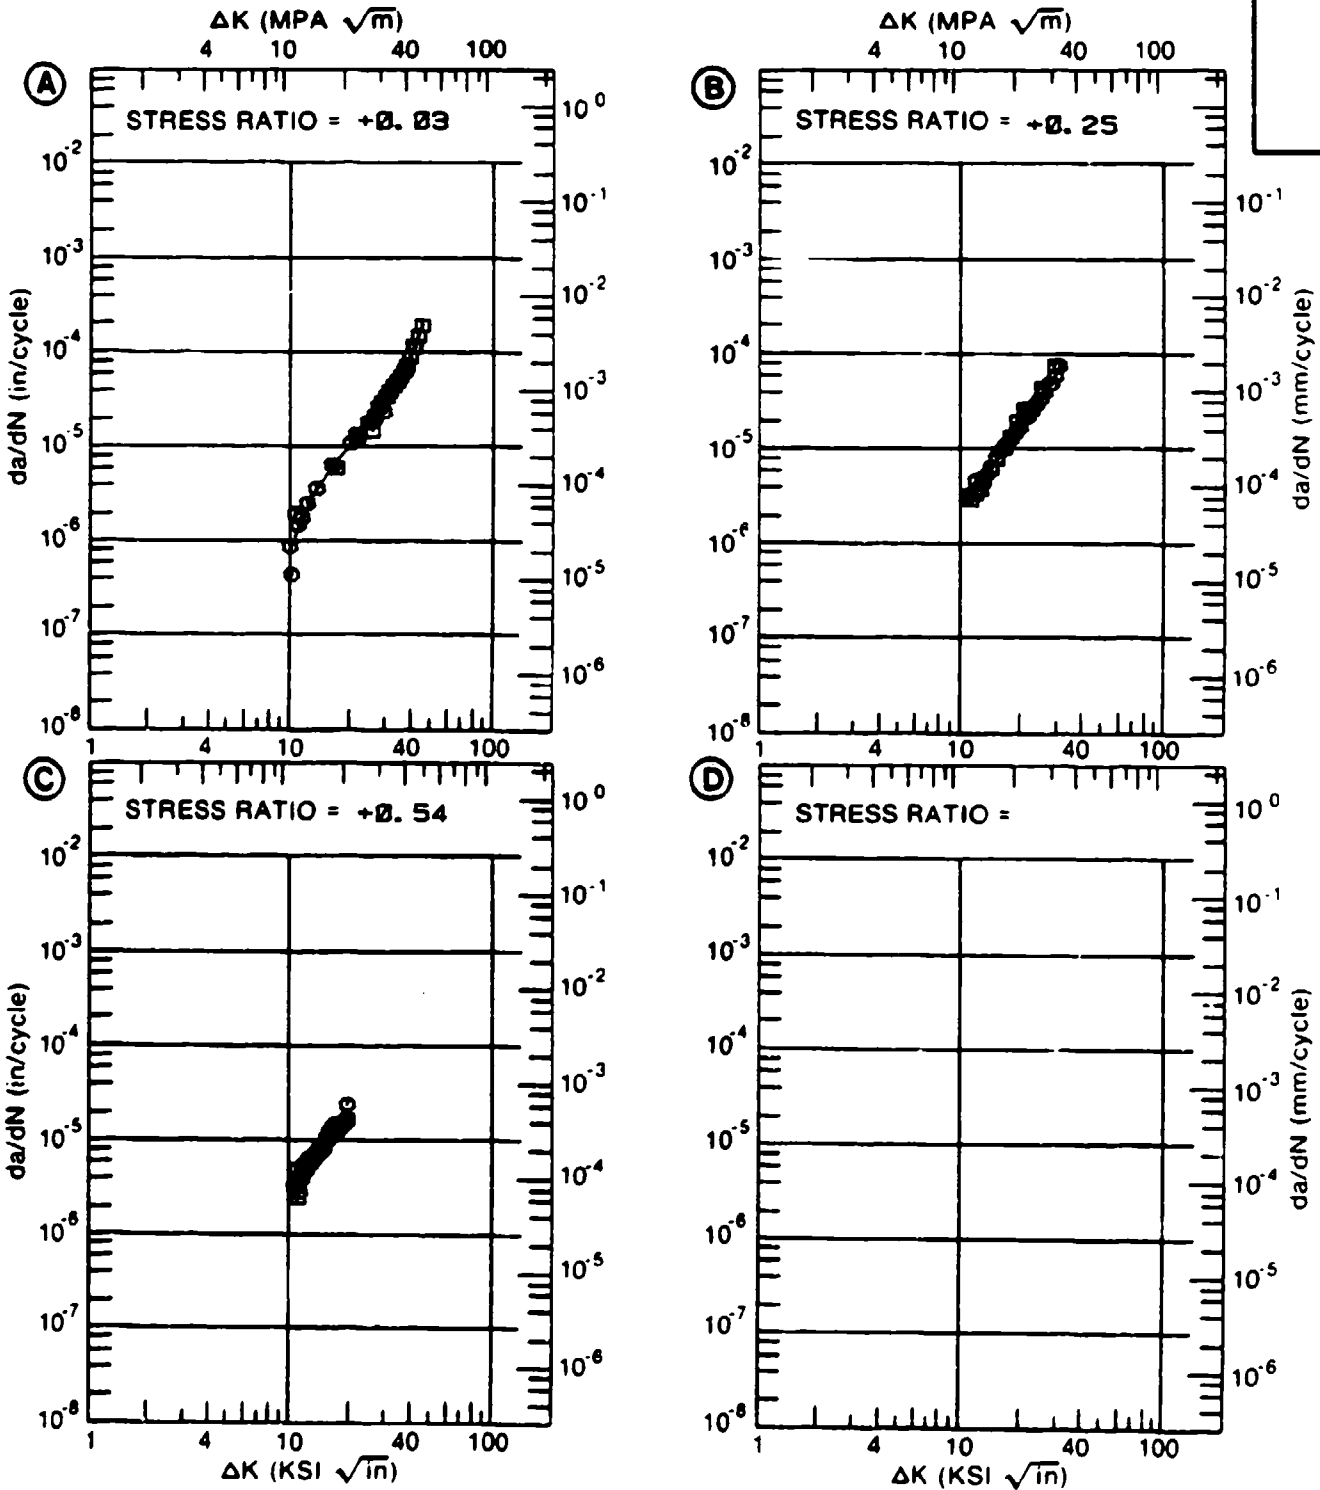


Figure 4.11.3.121

TABLE 4.11.3.122

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.122 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: 1775F 1HR WQ, 1675F 1HR WQ, 1000F-1200F
2-BHRS AC
ENVIRONMENT: + 300F, AIR

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	R=+0.03	R=+0.25	R=+0.54	
DELTA K MIN	A: 9.83 B: 10.90 C: 11.42 D:	1.46	3.45	
	.687			
10.00	.746			
13.00	2.32	3.46	5.10	
16.00	4.94	6.88	8.22	
20.00	10.1	11.9		
25.00	19.7	20.9		
30.00	33.4	39.8		
35.00	52.7			
40.00	79.8			
DELTA K MAX	A: 41.12 B: 32.83 C: 18.98 D:	60.4	11.5	
	87.2			
ROOT MEAN SQUARE PERCENT ERROR	15.61	21.04	6.65	

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1775F 1HR WQ, 1675F 1HR WQ, 1000F-1200F 2-8HRS AC
 FORM: 0.94" TH DISK
 SPECIMEN TYPE: KB BAR
 ORIENTATION: C-R
 FREQUENCY: 0.33 HZ
 ENVIRONMENT: + 300° F. AIR

YIELD STRENGTH: 150.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.252"
 SPECIMEN WIDTH: 0.991- 0.999"
 REFERENCES GE007

TITAN.
 ALLOY

TI-6AL-
 4V

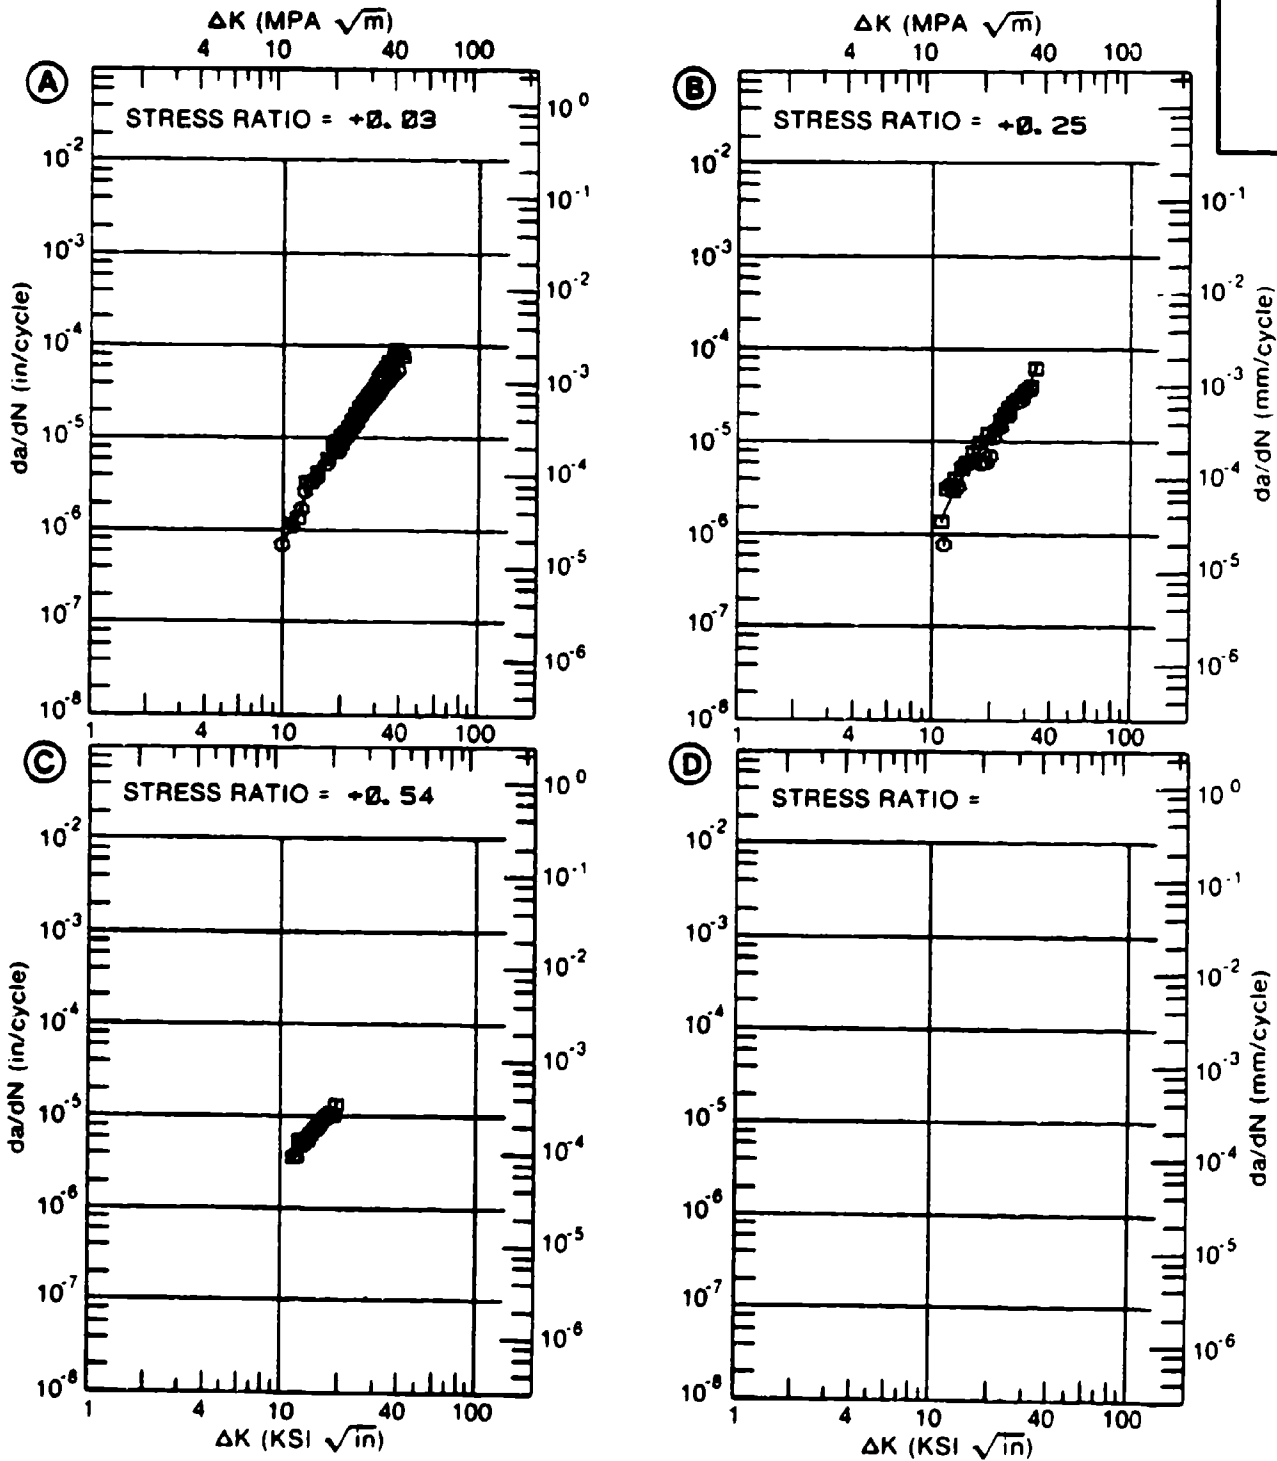


Figure 4.11.3.122

TABLE 4.11.3.123

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.123 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: 1775F 1HR WQ, 1675F 1HR WQ, 1000F-1200F
2-8HRS AC
ENVIRONMENT: + 600F, AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.03	R=+0.25	R=+0.54	
DELTA K	A: 8.19	.501			
MIN	B: 9.28		1.84		
	C: 8.94			1.96	
	D:				
	9.00	.715		1.96	
	10.00	1.05	2.04	2.12	
	13.00	2.57	3.70	4.38	
	16.00	4.99	6.85	8.94	
	20.00	9.87	13.3		
	25.00	19.2	22.6		
	30.00	32.9	28.3		
	35.00	52.0			
	40.00	77.8			
DELTA K	A: 42.82	95.8			
MAX	B: 30.82		28.7		
	C: 19.48			13.6	
	D:				
ROOT MEAN SQUARE		11.62	14.03	14.72	
PERCENT ERROR					

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1775F 1HR WQ, 1675F 1HR WQ, 1000F-1200F 2-8HRS AC
 FORM: 0.94" TH DISK
 SPECIMEN TYPE: KB BAR
 ORIENTATION: C-R
 FREQUENCY: 0.33 HZ
 ENVIRONMENT: + 600° F, AIR

YIELD STRENGTH: 150.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.251- 0.253"
 SPECIMEN WIDTH: 0.995- 1.002"
 REFERENCES: GE007

TITAN.
ALLOY

TI-6AL-
4V

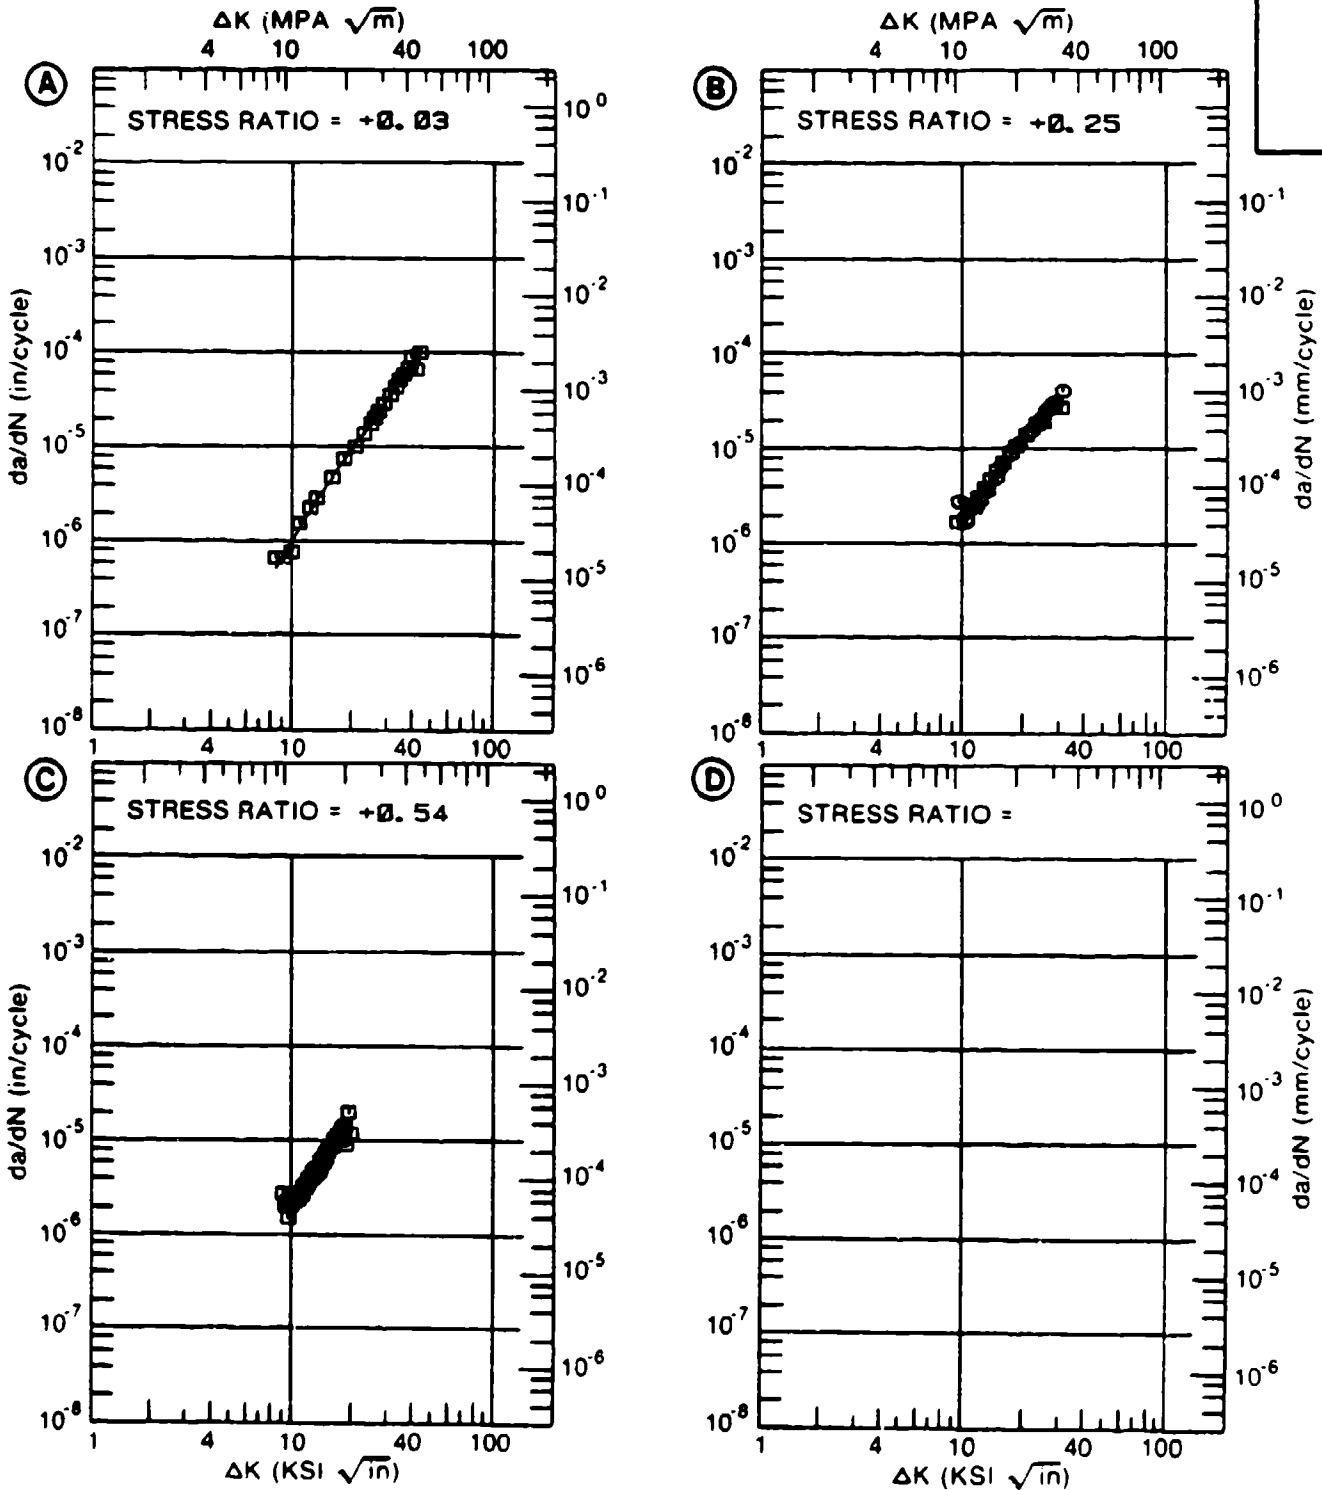


Figure 4.11.3.123

TABLE 4.11.3.124

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.11.3.124 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V
 CONDITION: 1775F 1HR WQ, 1675F 1HR WQ, 1000F-1200F
 2-8HRS AC
 ENVIRONMENT: + 600F, AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.03			
DELTA K	A: 8.01	.906			
MIN	B:				
	C:				
	D:				
	9.00	1.29			
	10.00	1.77			
	13.00	3.85			
	16.00	6.94			
	20.00	12.6			
	25.00	21.6			
	30.00	32.2			
	35.00	43.5			
	40.00	54.6			
DELTA K	A: 42.55	60.1			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		7.35			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: 1775F 1HR WQ, 1675F 1HR WQ, 1000F-1200F 2-8HRS AC
 FORM: 1.15" TH DISK
 SPECIMEN TYPE: KB BAR
 ORIENTATION: C-R
 FREQUENCY: 0.33 HZ
 ENVIRONMENT: + 800° F, AIR

YIELD STRENGTH: 145.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.251"
 SPECIMEN WIDTH: 1.000"
 REFERENCES: GE007

TITAN.
 ALLOY

TI-6AL-
 4V

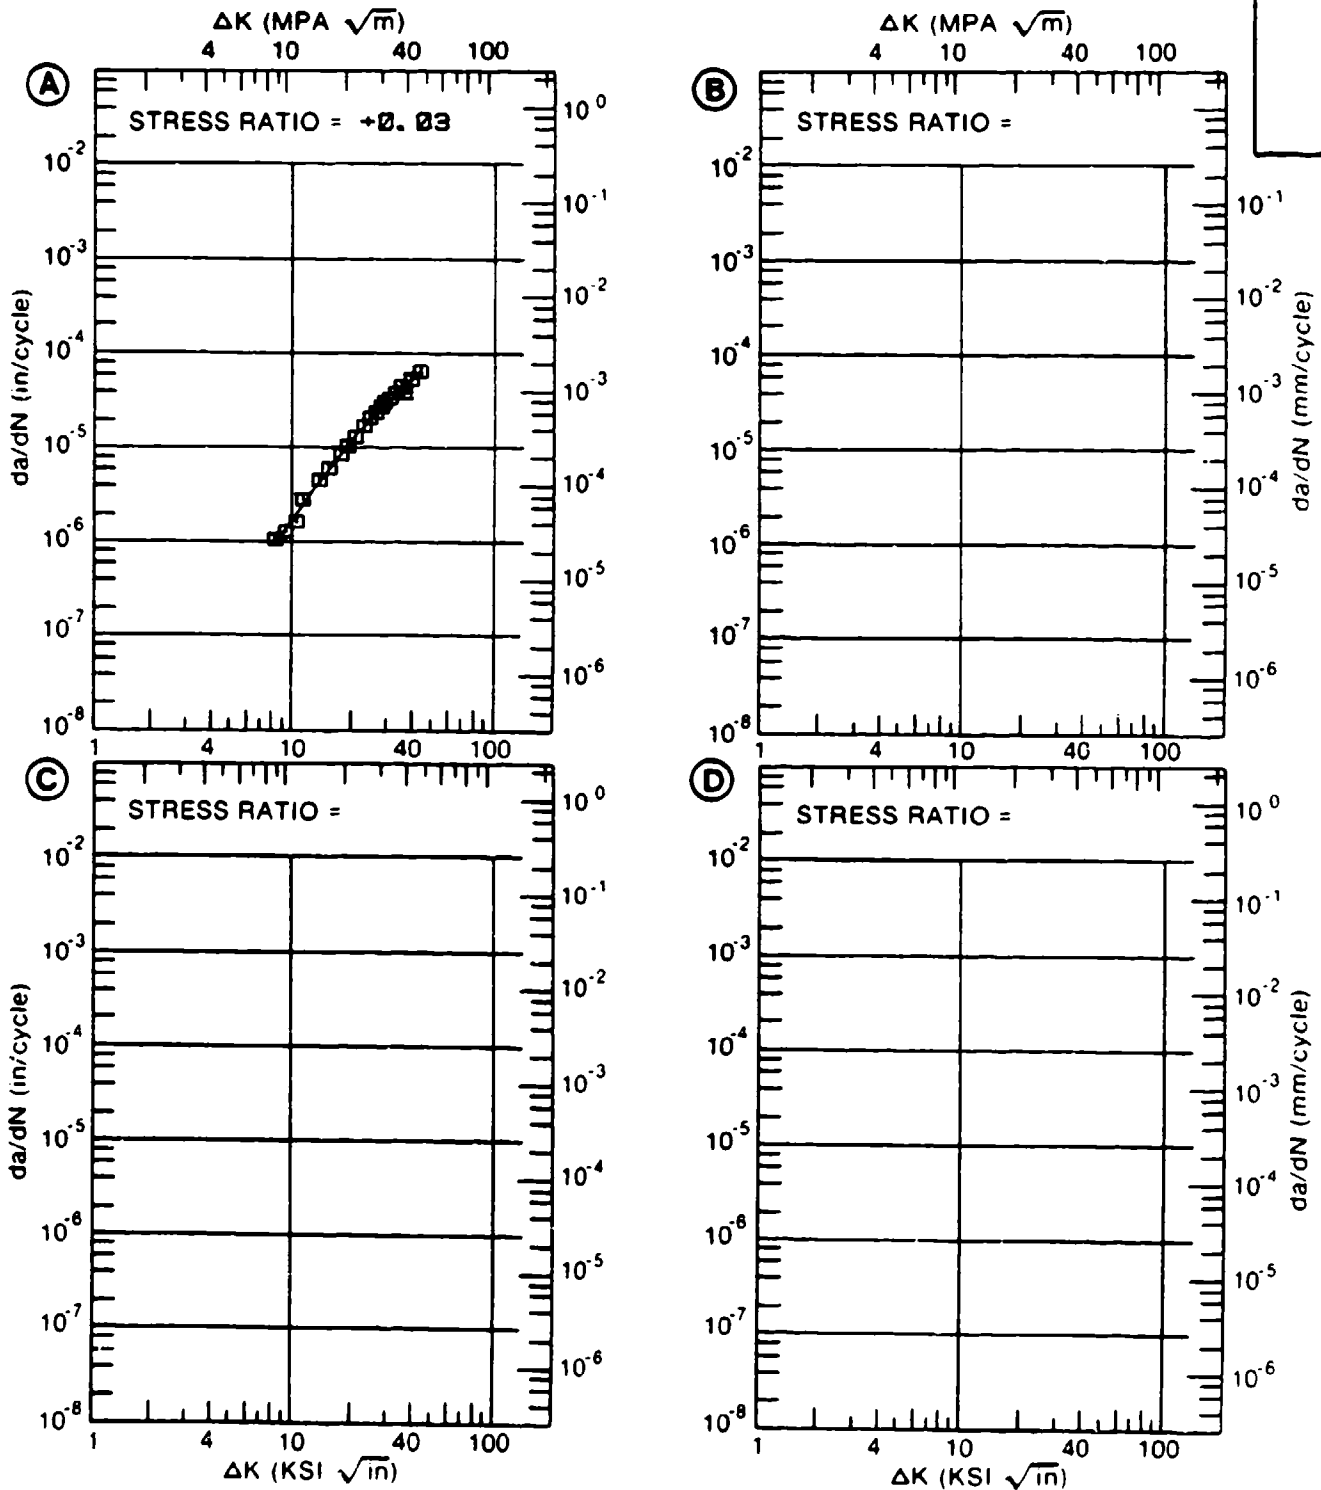


Figure 4.11.3.124

TABLE 4.11.3.125

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.125 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: 1950F 4HRS WG, 1000F 4HRS ARGON COOLED					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		ARGON			
DELTA K	A: 10.04	.179			
MIN	B:				
	C:				
	D:				
	13.00	.508			
	16.00	1.08			
	20.00	2.38			
	25.00	5.58			
	30.00	12.3			
	35.00	26.6			
	40.00	56.9			
	50.00	257.			
DELTA K	A: 50.06	260.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		57.10			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: 1950F 4HRS WQ, 1000F 4HRS ARGON COOLED
 FORM: FORGING
 SPECIMEN TYPE: WOL
 ORIENTATION: R-C
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH: 136.4 KSI
 ULT. STRENGTH: 147.9 KSI
 SPECIMEN THK: 0.800"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: UM001

TITAN.
 ALLOY

TI-6AL-
 4V

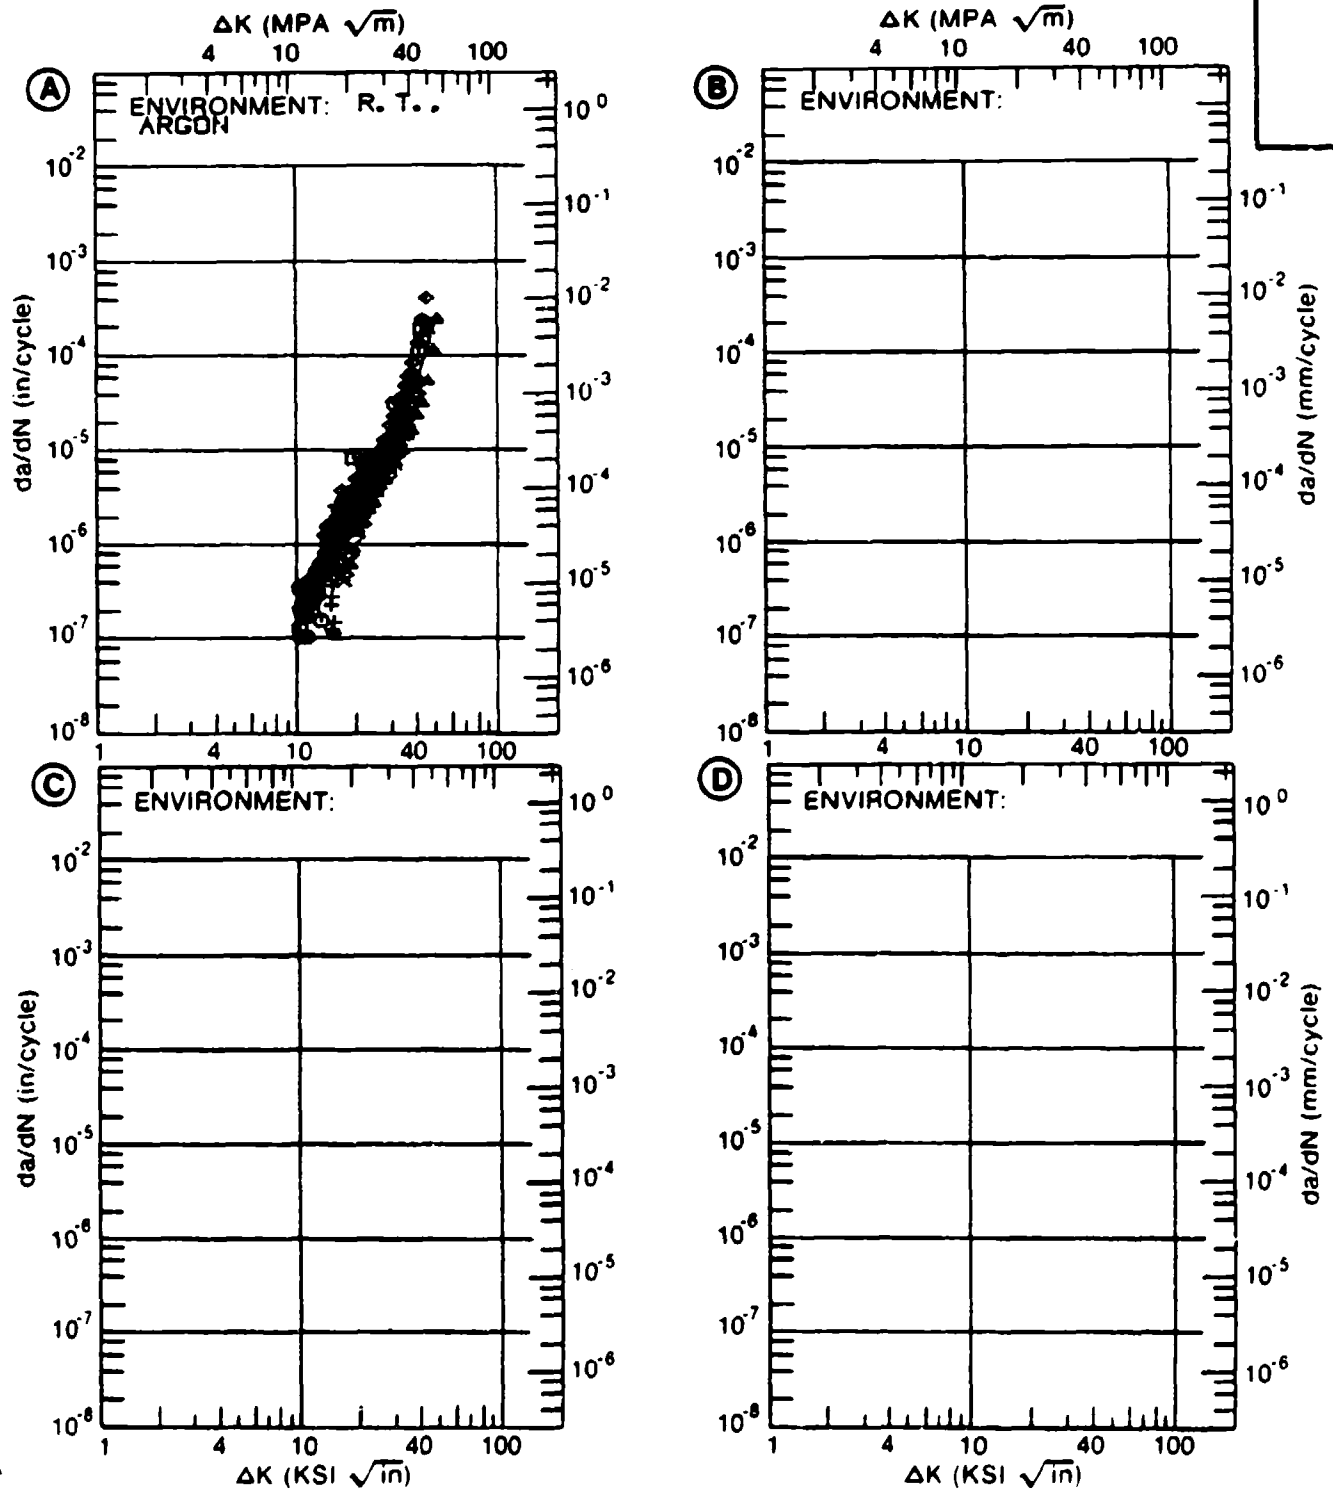


Figure 4.11.3.125

TABLE 4.11.3.126

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.126 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
CONDITION: 1950F 4HRS WQ, 1000F 4HRS ARGON COOLED

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. : ARGON			
DELTA K	A: 11.18	.159			
MIN	B:				
	C:				
	D:				
	13.00	.442			
	16.00	1.31			
	20.00	3.37			
	25.00	8.42			
	30.00	20.3			
	35.00	51.3			
DELTA K	A: 35.49	56.4			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 39.65
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1950F 4HRS WQ, 1000F 4HRS ARGON COOLED
 FORM: FORGING
 SPECIMEN TYPE: WOL
 ORIENTATION: C-R
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH: 136.4 KSI
 ULT. STRENGTH: 147.8 KSI
 SPECIMEN THK: 0.800"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: UM001

TITAN.
ALLOY

TI-6AL-
4V

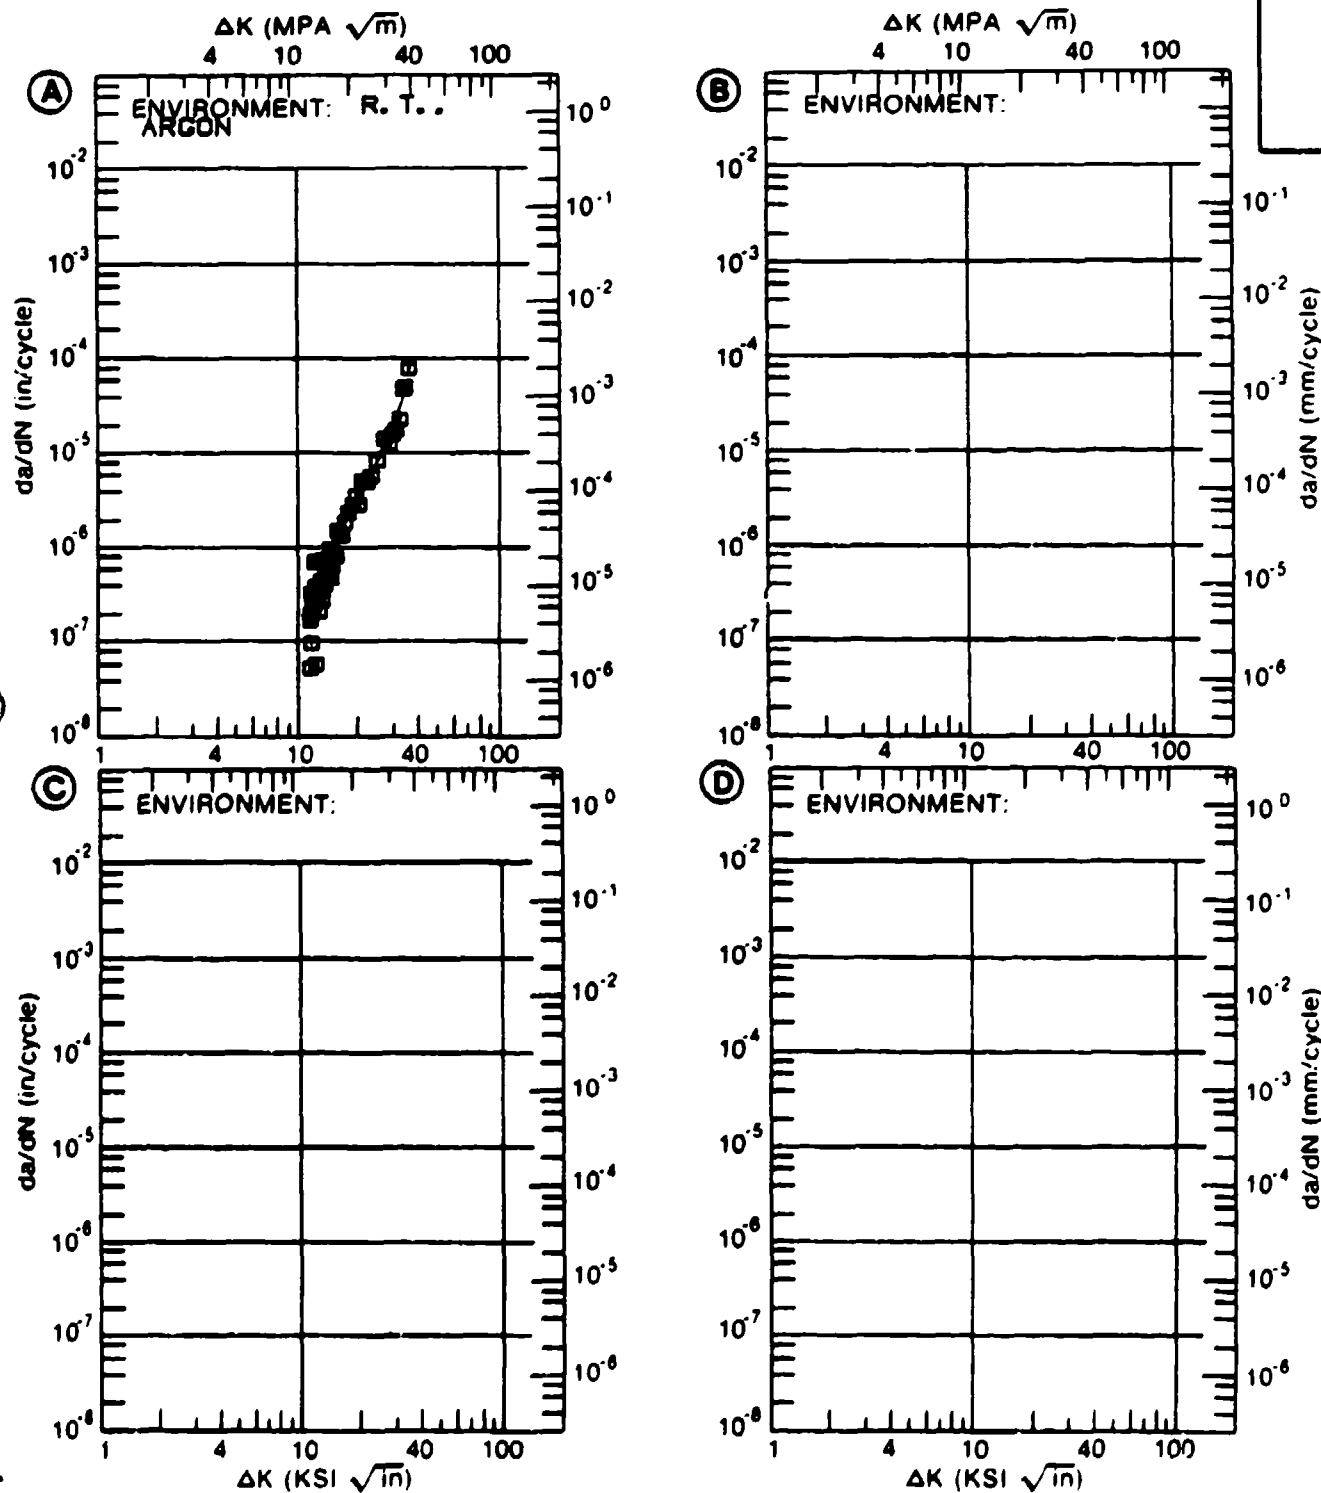


Figure 4.11.3.126

TABLE 4.11.3.127

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.11.3.127 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V
 CONDITION: EB WELD, STRESS RELIEVED (HEAT AFFECTED
 ZONE)

K MAX (KSI*IN**1/2)	DA/DT (10**-6 IN/HOUR)			
	A	B	C	D
	E=		E=	
	3.5% NACL; 75F		AIR; 175F	
K MAX MIN	A:	B:	C:	D:
200.00				
K MAX MAX	A:	B:	C:	D:
ROOT MEAN SQUARE PERCENT ERROR	0.00	0.00		

CONDITION/HT: EB WELD, STRESS RELIEVED (HEAT AFFECTED ZONE)
 FORM: 1.0" TH WELDMENT
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 YIELD STRENGTH: 132.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.550"
 CRACK LENGTH (A₀):
 K_{ISCC}: 33.00 KSI (SQRT IN)
 REFERENCES: 88144

TITAN.
ALLOY

TI-6AL-4V

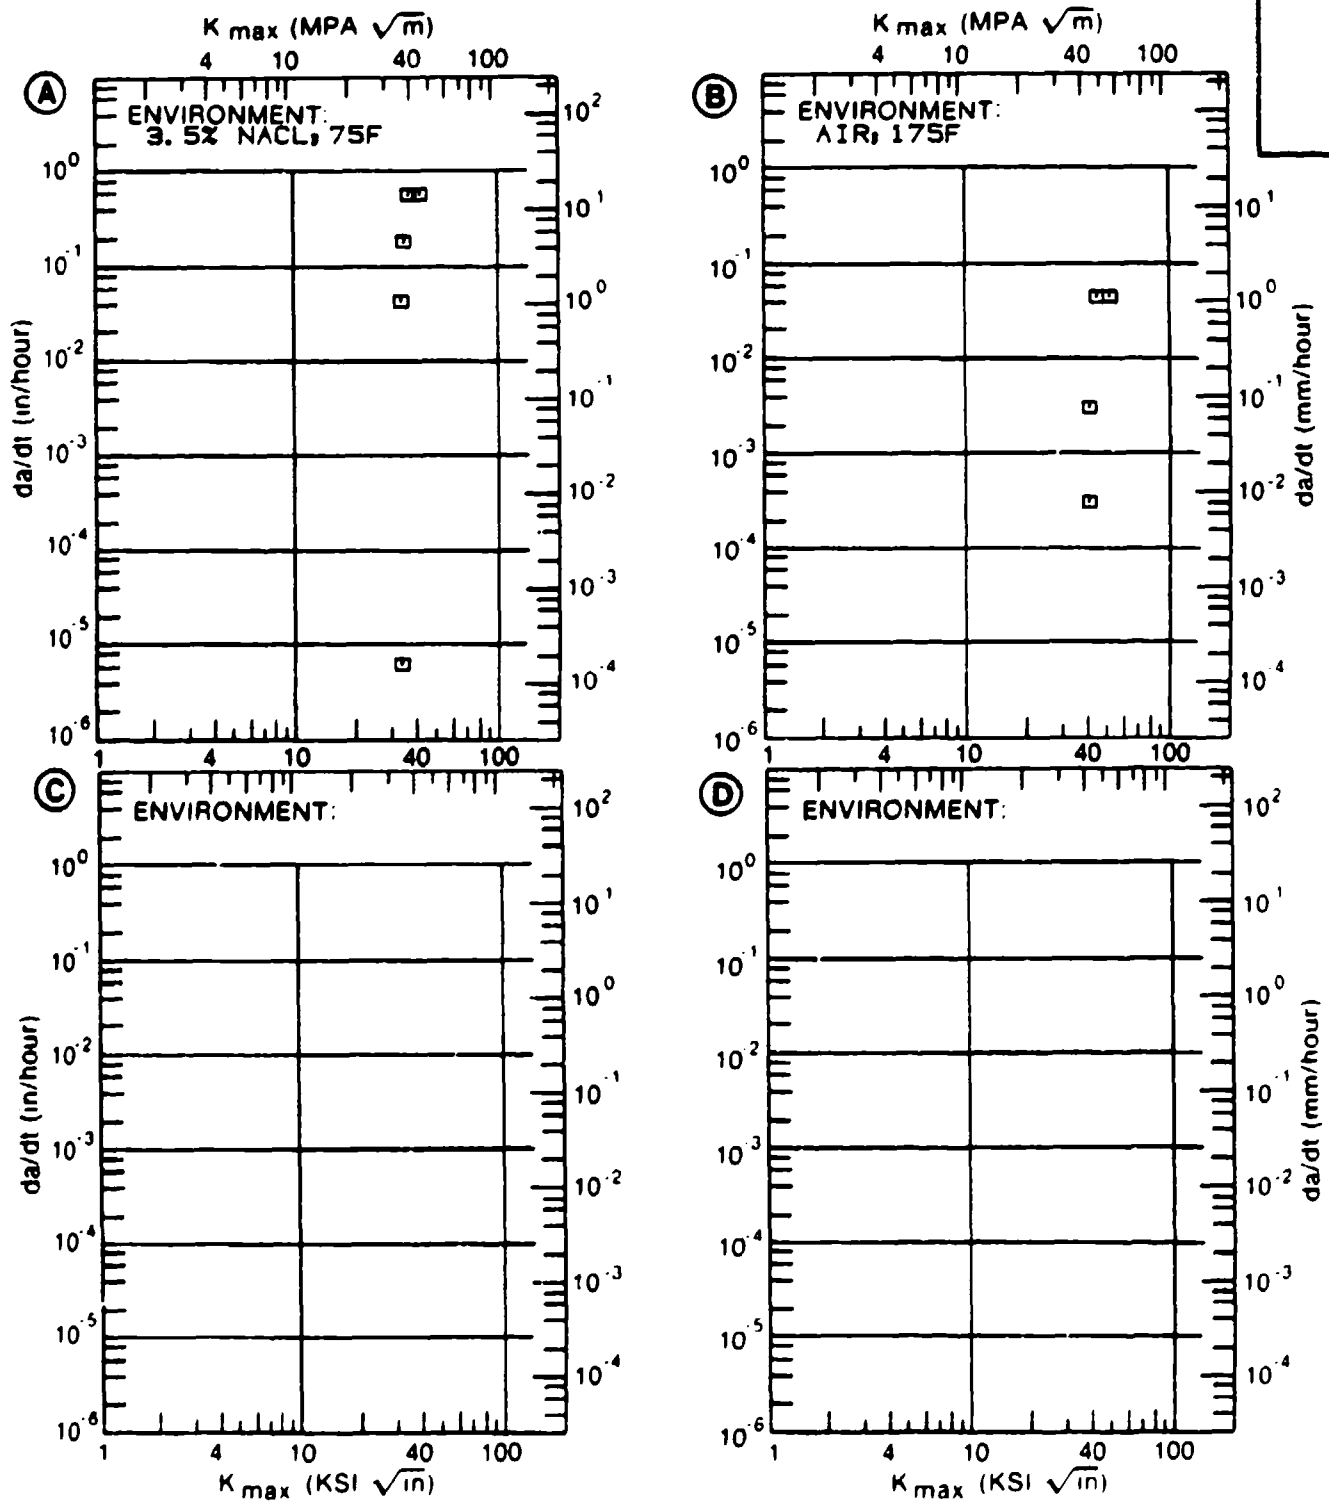


Figure 4.11.3.127

TABLE 4.11.3.128

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.128 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: EB WELD, STRESS RELIEVED (WELD ZONE)					
K MAX (KSI*IN**1/2)		DA/DT (10**--6 IN/HOUR)			
		A	B	C	D
		E=	E=		
		3.5% NACL; 75F		AIR; 175F	
K MAX	A: 36.00	171.			
MIN	B:				
	C:				
	D:				
	40.00	724548.			
K MAX	A: 44.00	964781.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		48.35	0.00		
PERCENT ERROR					

CONDITION/HT: EB WELD, STRESS RELIEVED (WELD ZONE)
 FORM: 1.0" TH WELDMENT
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 YIELD STRENGTH: 132.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.550"
 CRACK LENGTH (A₀):
 K_{ISCC}: 36.00 KSI (SQRT IN)
 REFERENCES: 08144

TITAN.
 ALLOY
 TI-6AL-
 4V

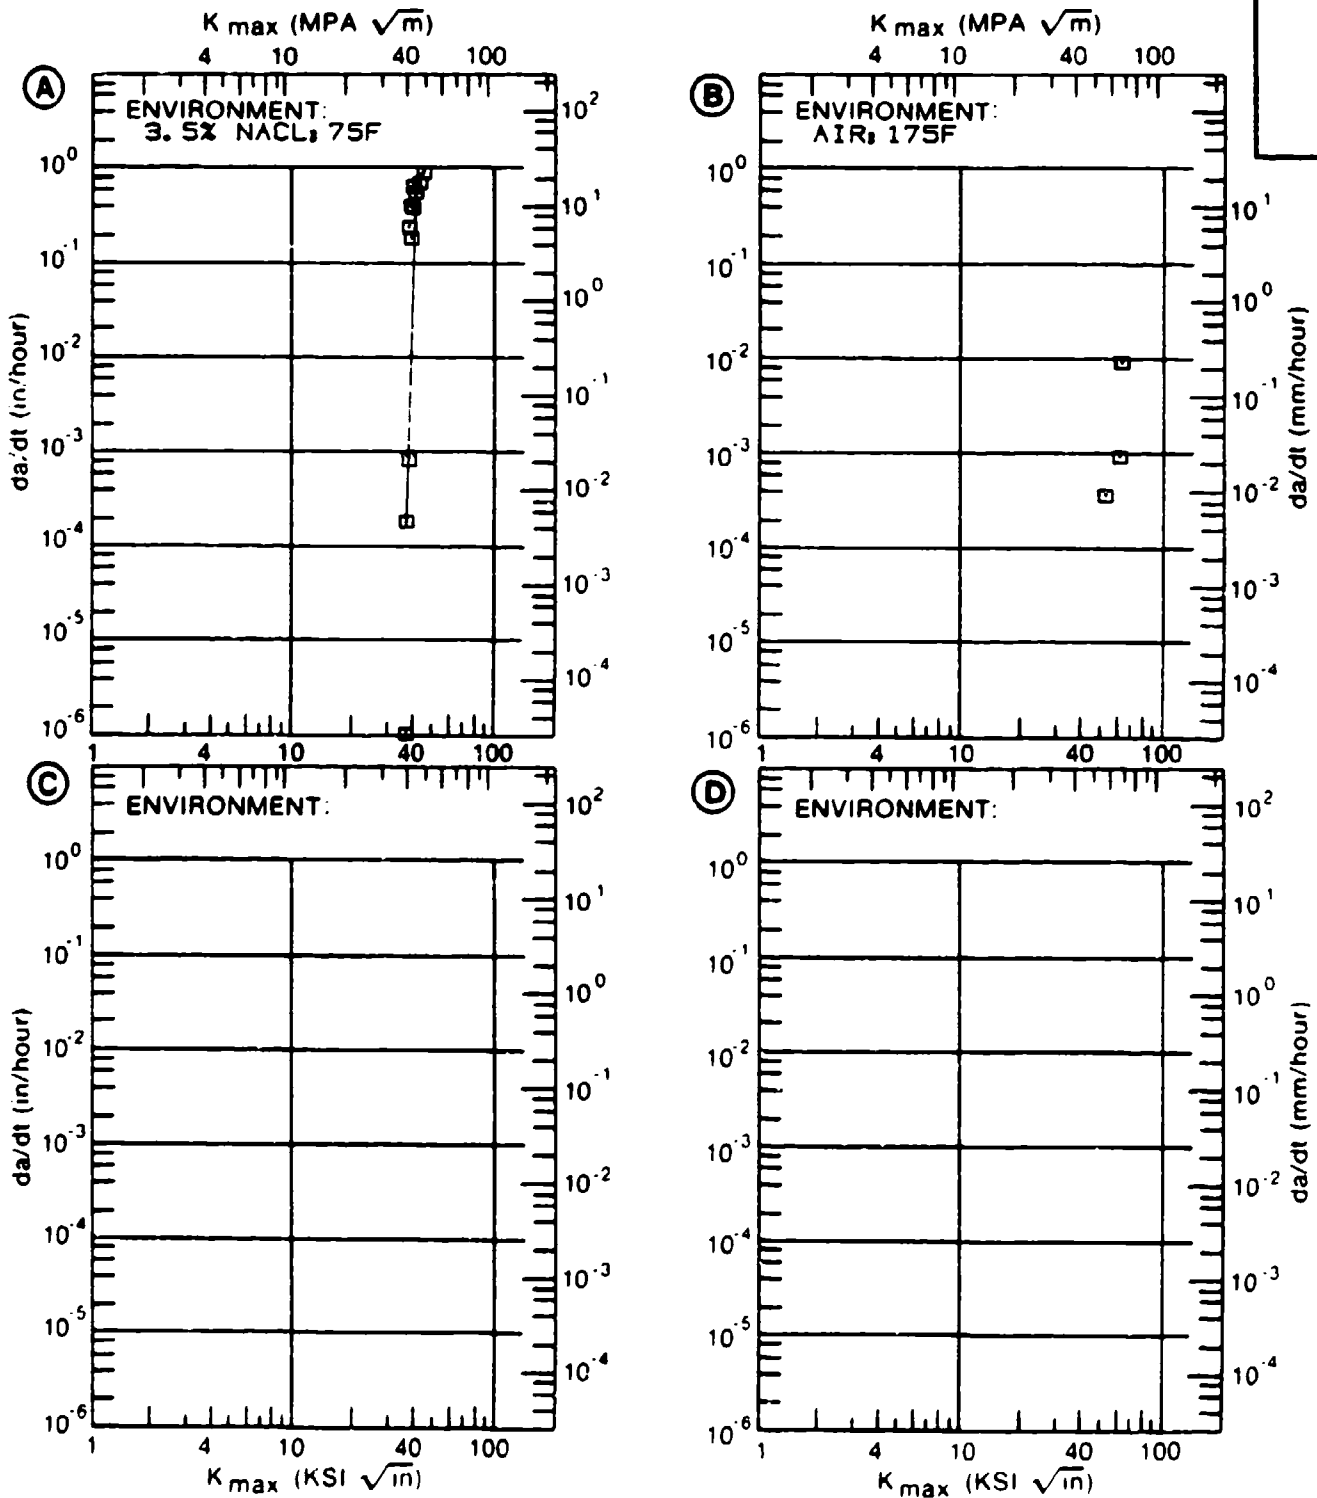


Figure 4.11.3.128

TABLE 4.11.3.129

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.11.3.129 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
K MAX (KSI*IN**1/2)		DA/DT (10** ⁻³ IN/HOUR)			
		A	B	C	D
		E= R. T. 0.6M KCL -500 MV		E= R. T. 0.6M KCL -1000 MV	
K MAX MIN	A: 22.00	240.			
	B: 23.00		232.		
	C:				
	D:				
	25.00	542.	266.		
	30.00	854.	299.		
	35.00	933.	341.		
	40.00	1059.	474.		
K MAX MAX	A: 45.20	1499.			
	B: 45.20		867.		
	C:				
	D:				
ROOT MEAN SQUARE		13.23	13.95		
PERCENT ERROR					

CONDITION/HT: MA
 FORM: 0.2" TH SHEET
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 0.200"
 SPECIMEN WIDTH:
 CRACK LENGTH (A₀):
 K_{ISCC}:
 REFERENCES: 81221

TITAN.
 ALLOY

TI-6AL-
 4V

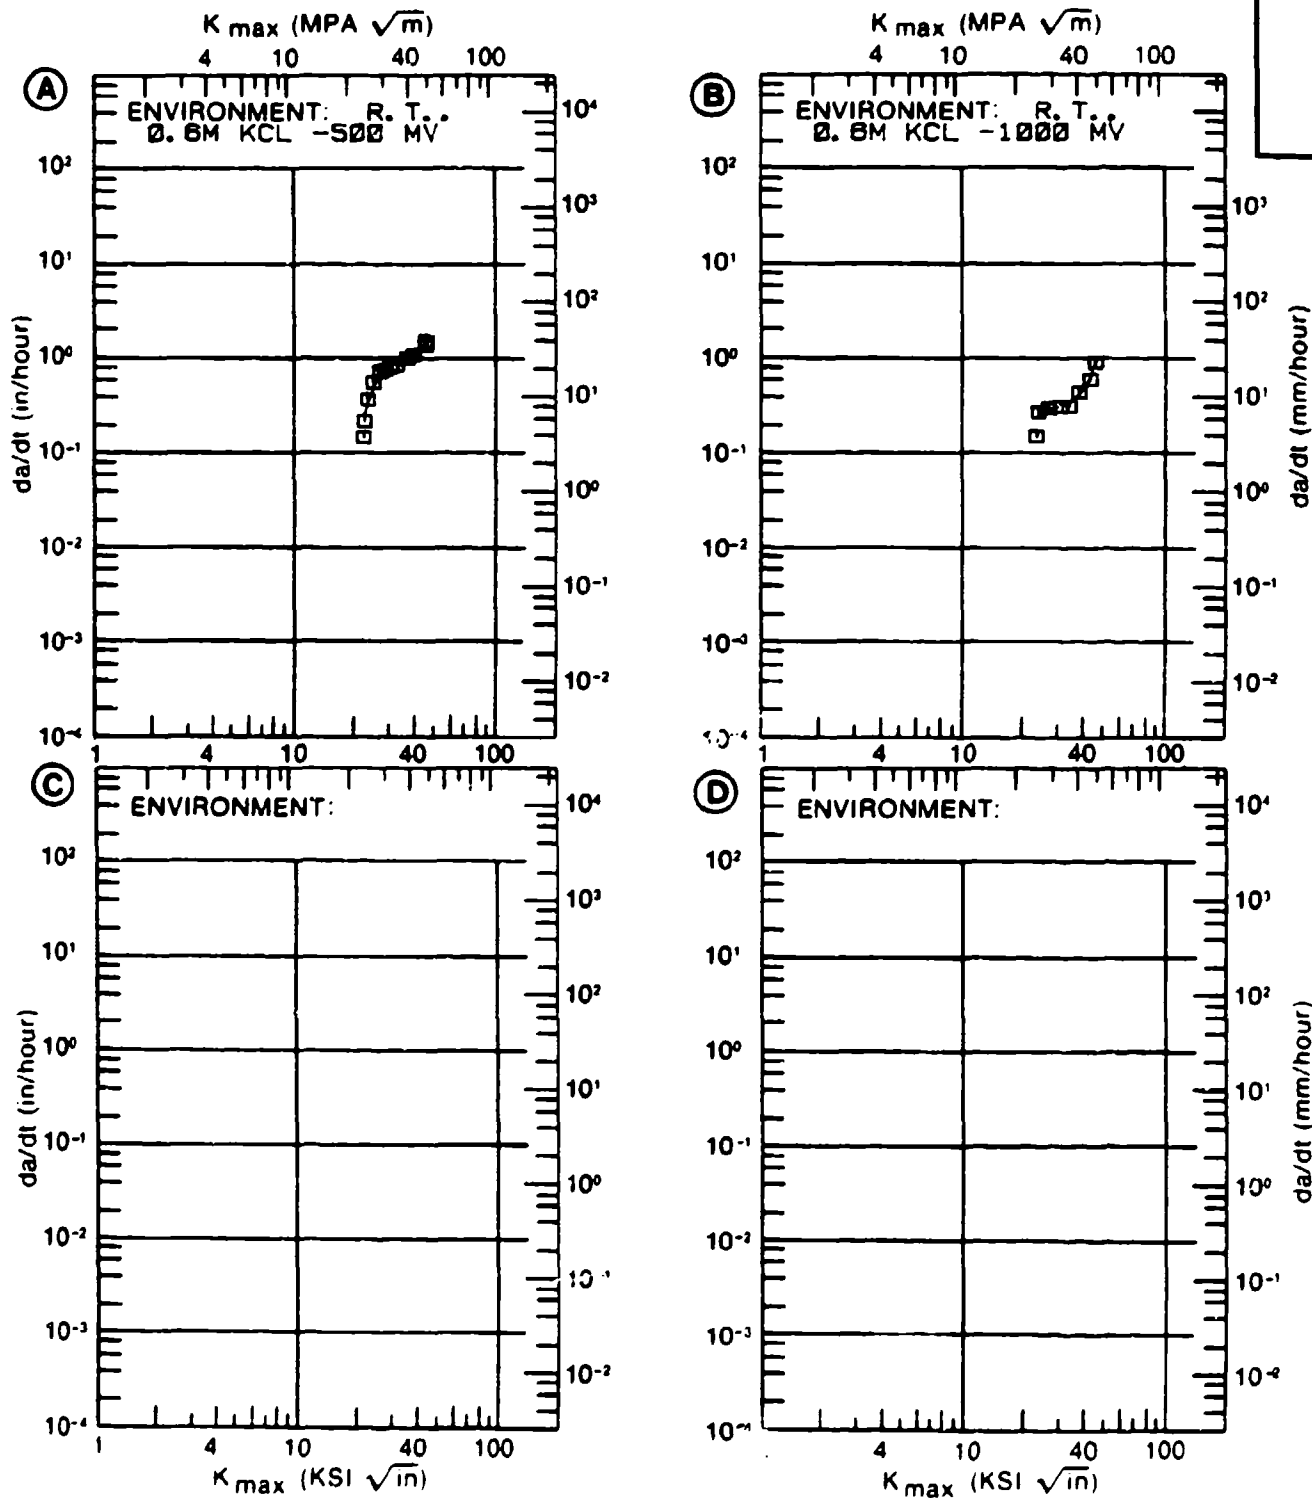


Figure 4.11.3.129

TABLE 4.11.3.130

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.11.3.130 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
K MAX (KSI*IN**1/2)		DA/DT (10**-3 IN/HOUR)			
		A	B	C	D
		E= R. T. 5M KI +1000 MV	E= R. T. 5M KI +500 MV	E= R. T. 5M KI 0 MV	E= R. T. 5M KI -500 MV
K MAX	A:				
MIN	B: 17.50		970.		
	C: 18.50			1202.	
	D: 19.20				1271.
	20.00		17493.	6645.	3216.
	25.00		26009.	15774.	9982.
	30.00		38482.	27636.	15327.
	35.00			42504.	21875.
	40.00			56727.	30115.
K MAX	A:				
MAX	B: 34.00		52976.		
	C: 44.80			65998.	
	D: 44.70				40011.
ROOT MEAN SQUARE		0.00	29.55	12.77	12.68
PERCENT ERROR					

CONDITION/HT: MA
 FORM: 0.2" TH SHEET
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 0.200"
 SPECIMEN WIDTH:
 CRACK LENGTH (A₀):
 K_{ISCC}:
 REFERENCES: 81221

TITAN.
 ALLOY

TI-6AL-4V

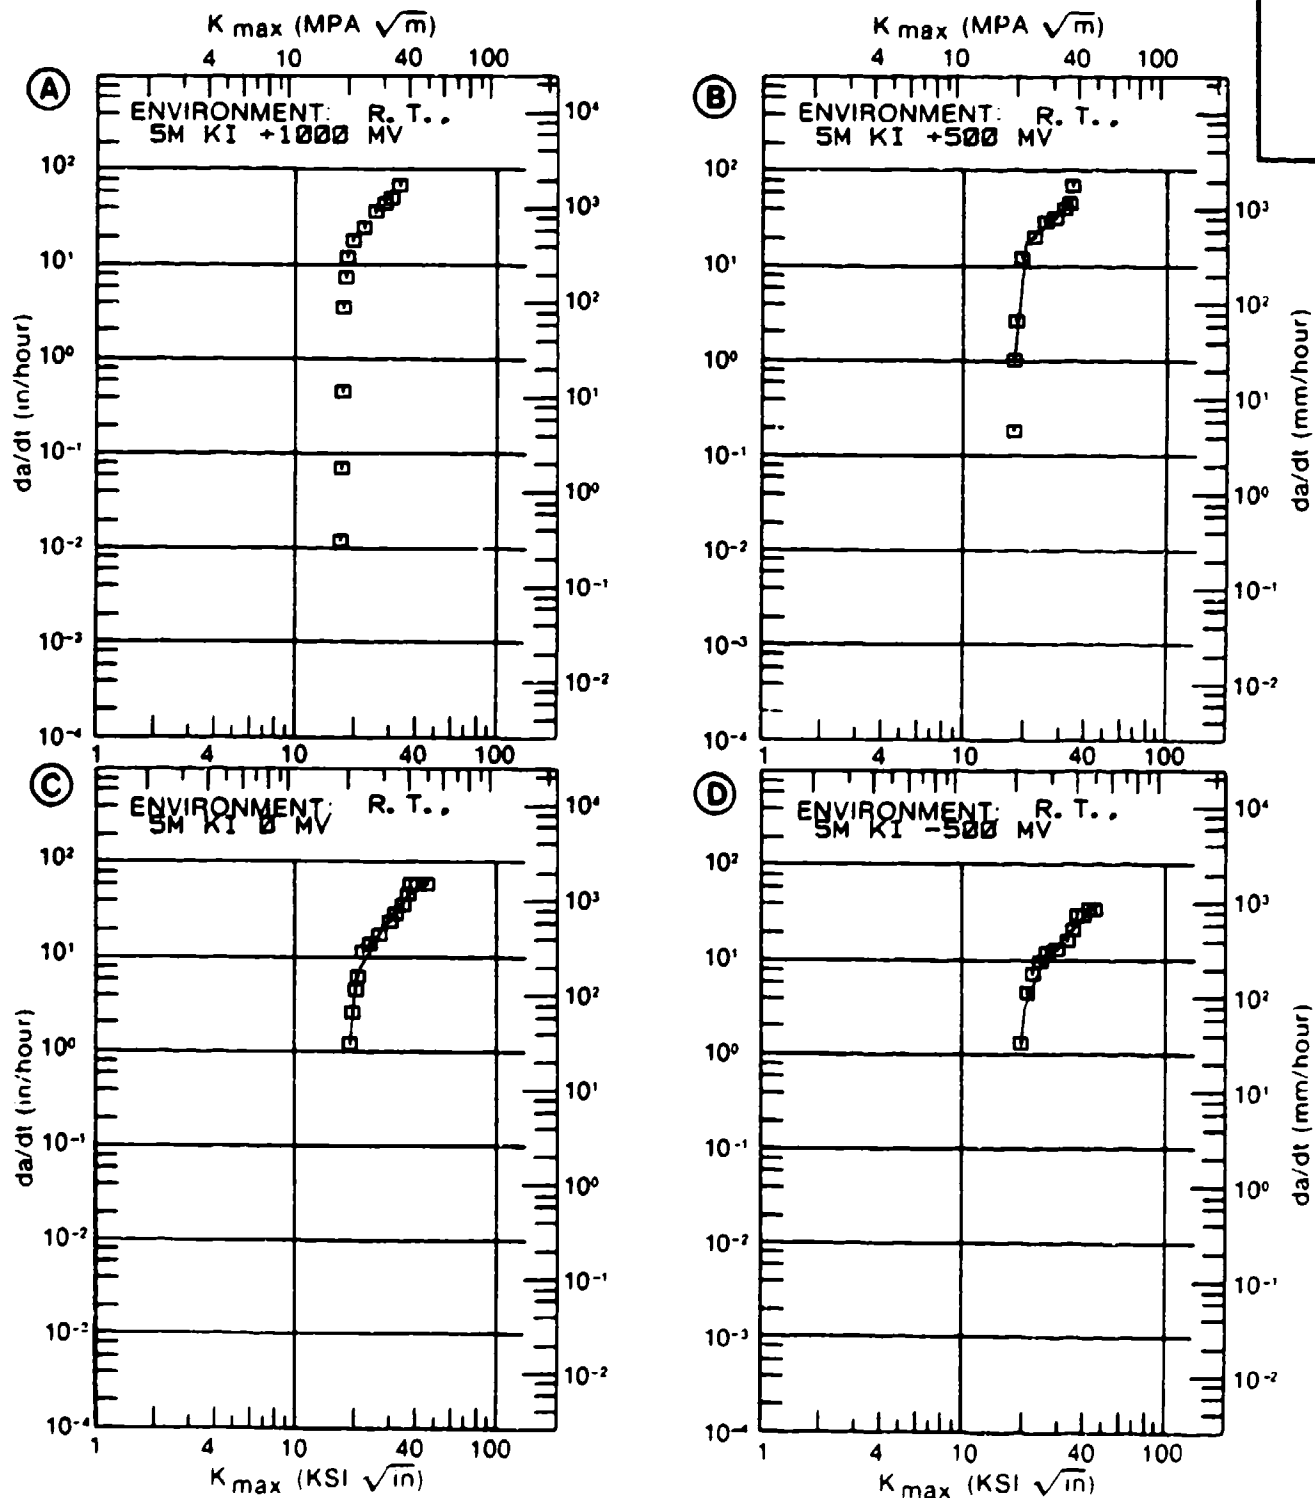


Figure 4.11.3.130

TABLE 4.11.3.131

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.11.3.131 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
K MAX (KSI*IN**1/2)		DA/DT (10**-3 IN/HOUR)			
		A	B	C	D
		E= R. T. 5M KI -1000 MV	E= R. T. 5M KI -1500 MV		
K MAX MIN	A:	30.00	1328.		
	B:				
	C:				
	D:				
		35.00	2562.		
		40.00	9680.		
K MAX MAX	A:	44.00	10010.		
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		11.47	0.00		
PERCENT ERROR					

CONDITION/HT: MA
 FORM: 0.2" TH SHEET
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 0.200"
 SPECIMEN WIDTH:
 CRACK LENGTH (A_c):
 K_{ISCC}:
 REFERENCES: 81221

TITAN.
 ALLOY

TI-6AL-
 4V

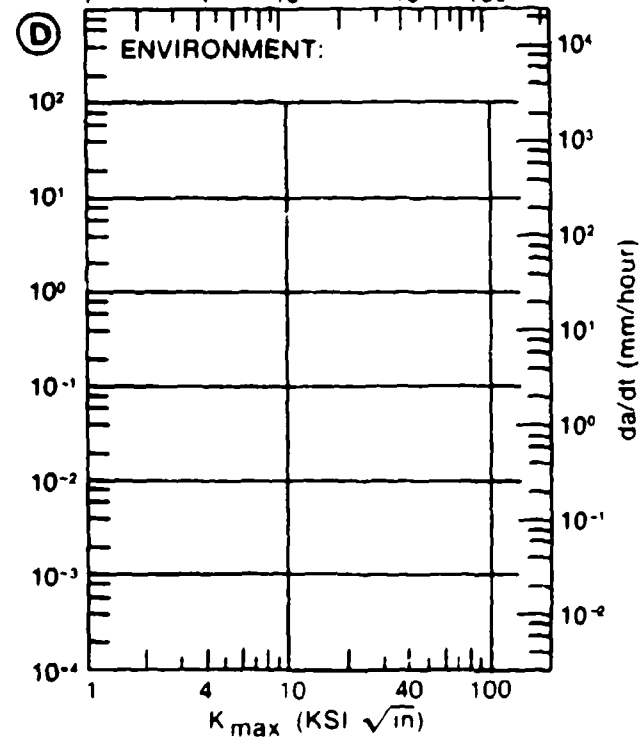
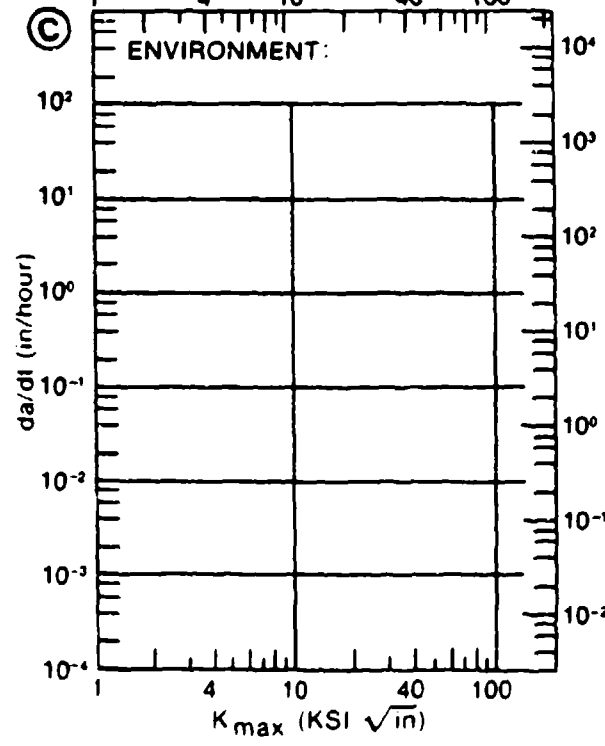
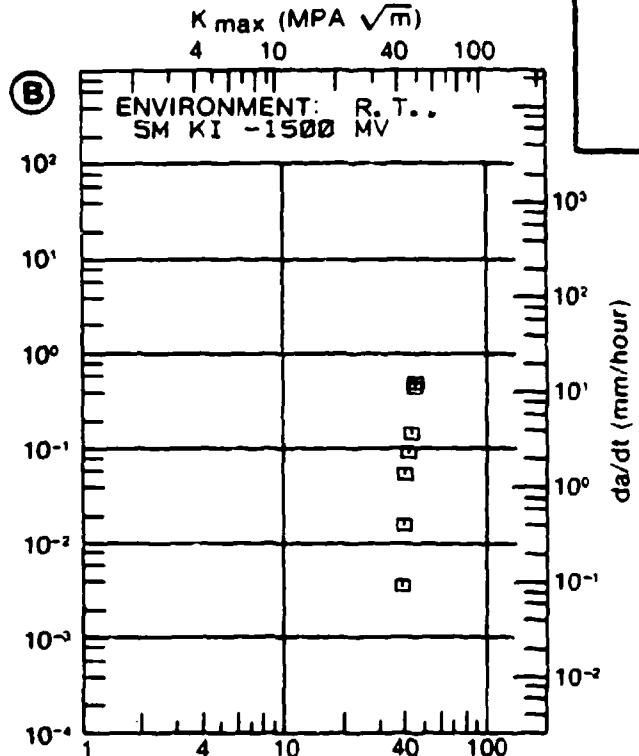
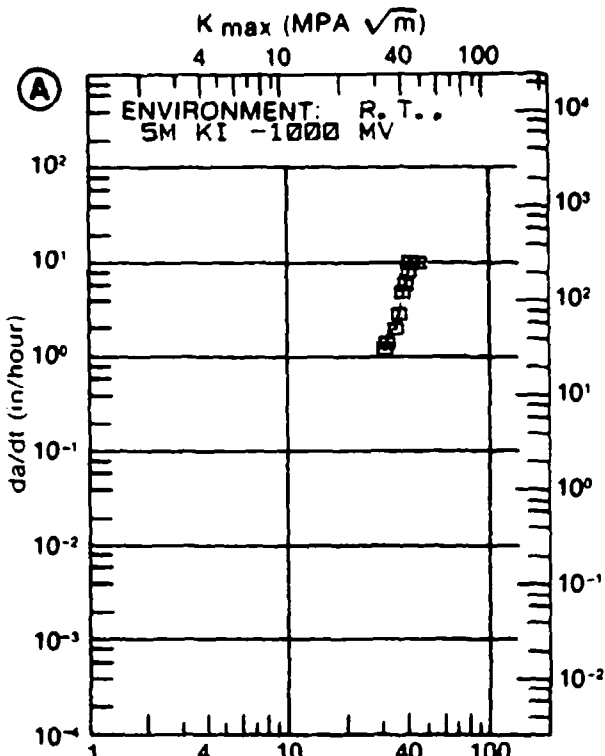


Figure 4.11.3.131

TABLE 4.11.3.132

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.11.3.132 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
K MAX (KSI*IN**1/2)		DA/DT (10** ⁻³ IN/HOUR)			
		A	B	C	D
		E= R. T. 6M KF	E= R. T. 3M KF	E= R. T. 1M KF	E= R. T. DIST. WATER
K MAX MIN	A: 30.00	461.			
	B:				
	C: 35.00			30.0	
	D: 31.40				196.
	35.00	1075.			381.
	40.00	2121.		207.	485.
K MAX MAX	A: 44.50	3590.			
	B:				
	C: 44.20			529.	
	D: 45.00				522.
ROOT MEAN SQUARE		11.57	0.00	11.33	2.17
PERCENT ERROR					

CONDITION/HT: MA
 FORM: 0.2" TH SHEET
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 0.200"
 SPECIMEN WIDTH:
 CRACK LENGTH (A₀):
 K_{ISCC}: 35.00 KSI (SQRT IN)
 REFERENCES: B1221

TITAN.
 ALLOY

TI-6AL-
 4V

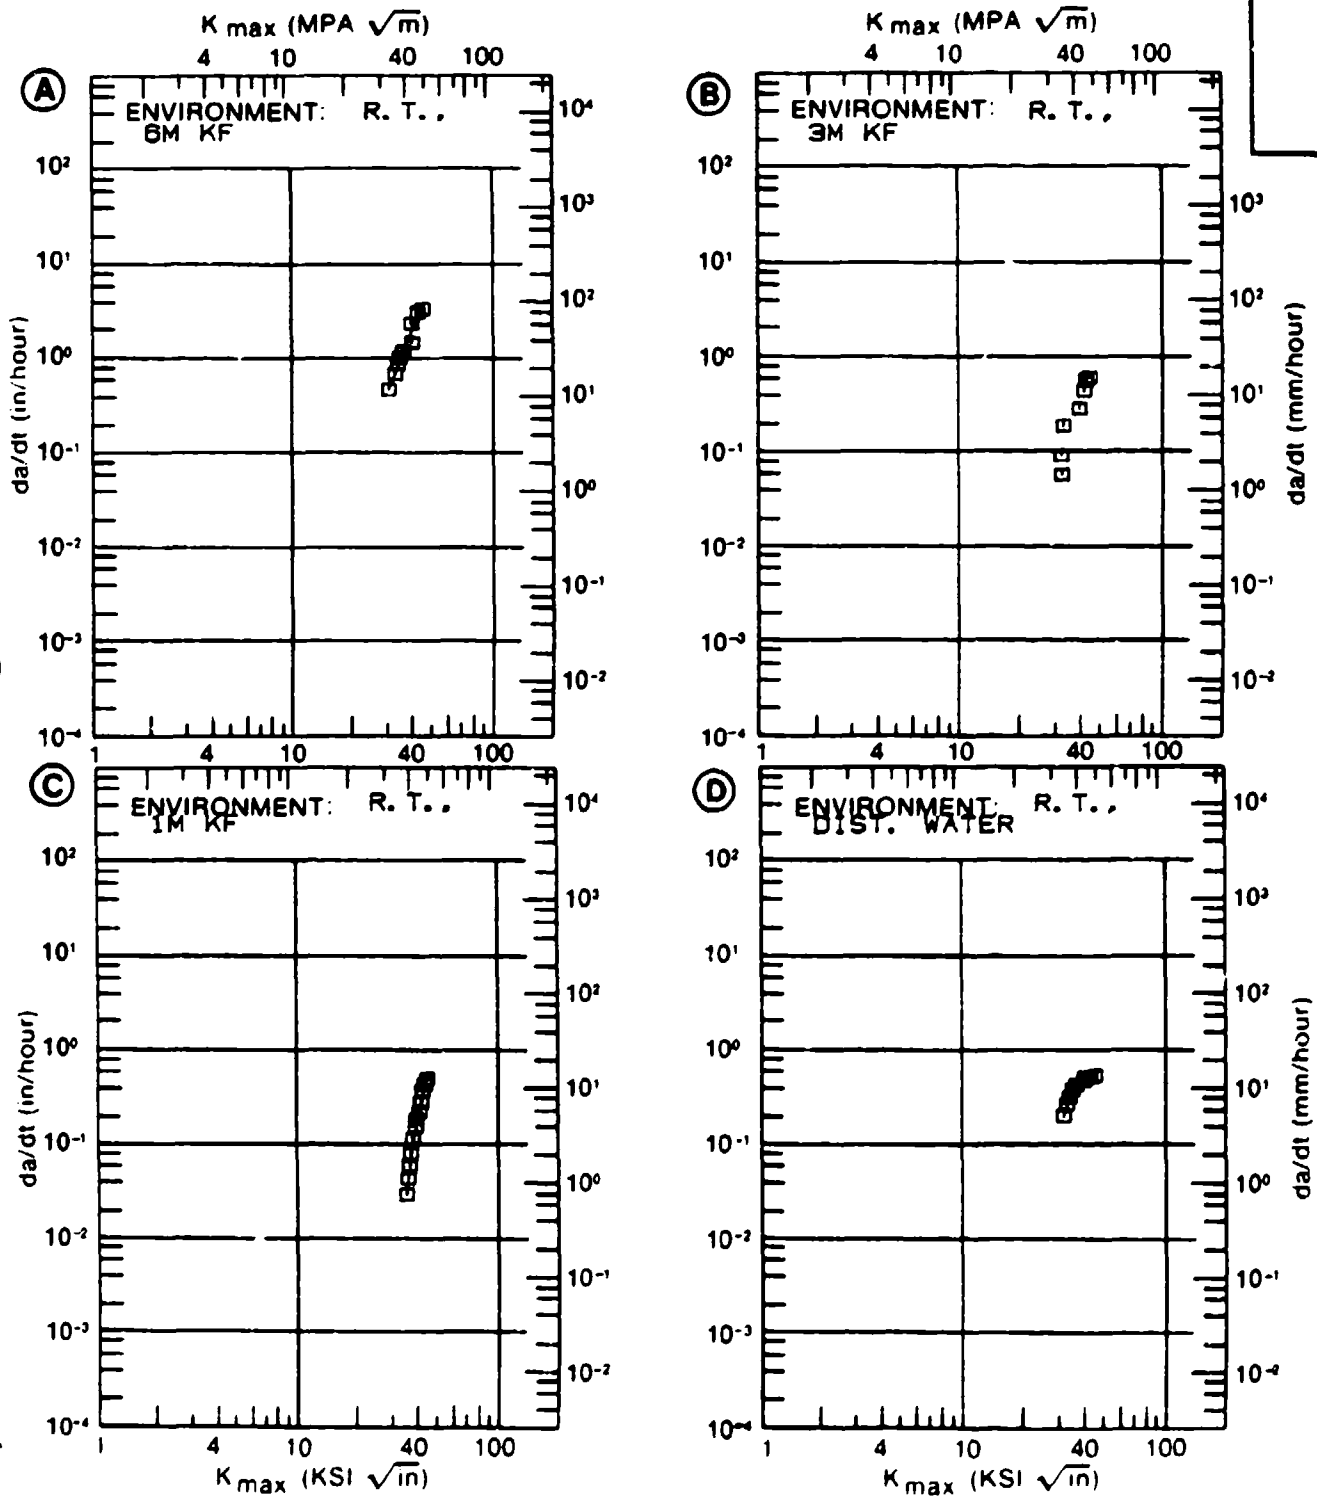


Figure 4.11.3.132

TABLE 4.11.3.133

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.11.3.133 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
K MAX (KSI*IN**1/2)		DA/DT (10** ⁻³ IN/HOUR)			
		A	B	C	D
		E= R. T. 0.6M KCL +2000 MV	E= R. T. 0.6M KCL +1000 MV	E= R. T. 0.6M KCL +500 MV	E= R. T. 0.6M KCL 0 MV
K MAX	A:		363.		
MIN	B:			882.	
	C:				576.
	D:				
	25.00		1708.	1236.	869.
	30.00		2448.	1823.	1303.
	35.00		3586.	2242.	1789.
	40.00		5102.	3027.	2398.
K MAX	A:				
MAX	B:		6844.		
	C:			5110.	
	D:				3230.
ROOT MEAN SQUARE		0.00	8.77	7.97	9.38
PERCENT ERROR					

CONDITION/HT: MA
 FORM: 0.2" TH SHEET
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 0.200"
 SPECIMEN WIDTH:
 CRACK LENGTH (A_0):
 K_{ISCC} :
 REFERENCES: 01221

TITAN.
 ALLOY

TI-6AL-
 4V

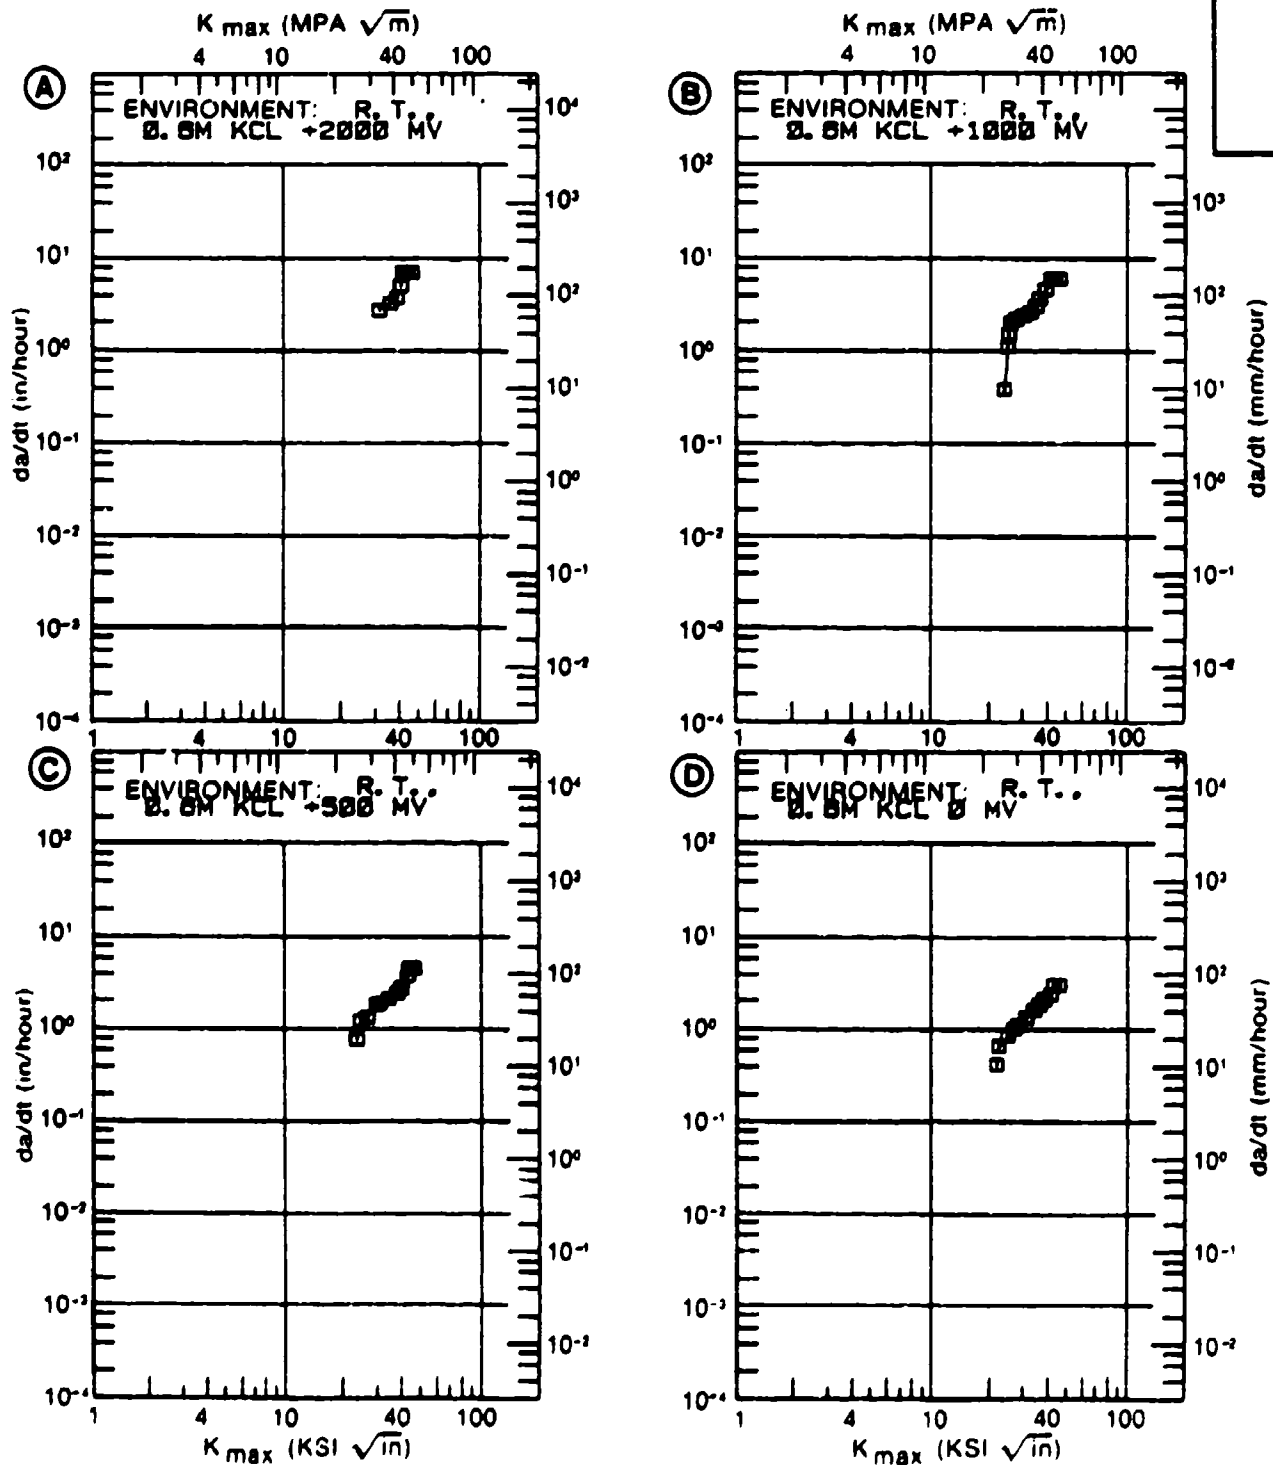


Figure 4.11.3.133

TABLE 4.11.3.134

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.134 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: MA					
K MAX (KSI*IN**1/2)		DA/DT (10**-3 IN/HOUR)			
		A	B	C	D
		E= R. T. 3. 5% NACL	E= R. T. JP-4 FUEL		
K MAX MIN	A: 30.00	.693			
	B:				
	C:				
	D:				
	35.00	1879.			
	40.00	2253.			
K MAX MAX	A: 45.00	4520.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		27.43	0.00		

CONDITION/HT: MA
 FORM: 1.0" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 YIELD STRENGTH: 132.0 KSI
 ULT. STRENGTH:

SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.550"
 CRACK LENGTH (A₀):
 K_{ISCC}: 30.0; 49.0 KSI
 REFERENCES: 00144

TITAN.
 ALLOY
 TI-6AL-
 4V

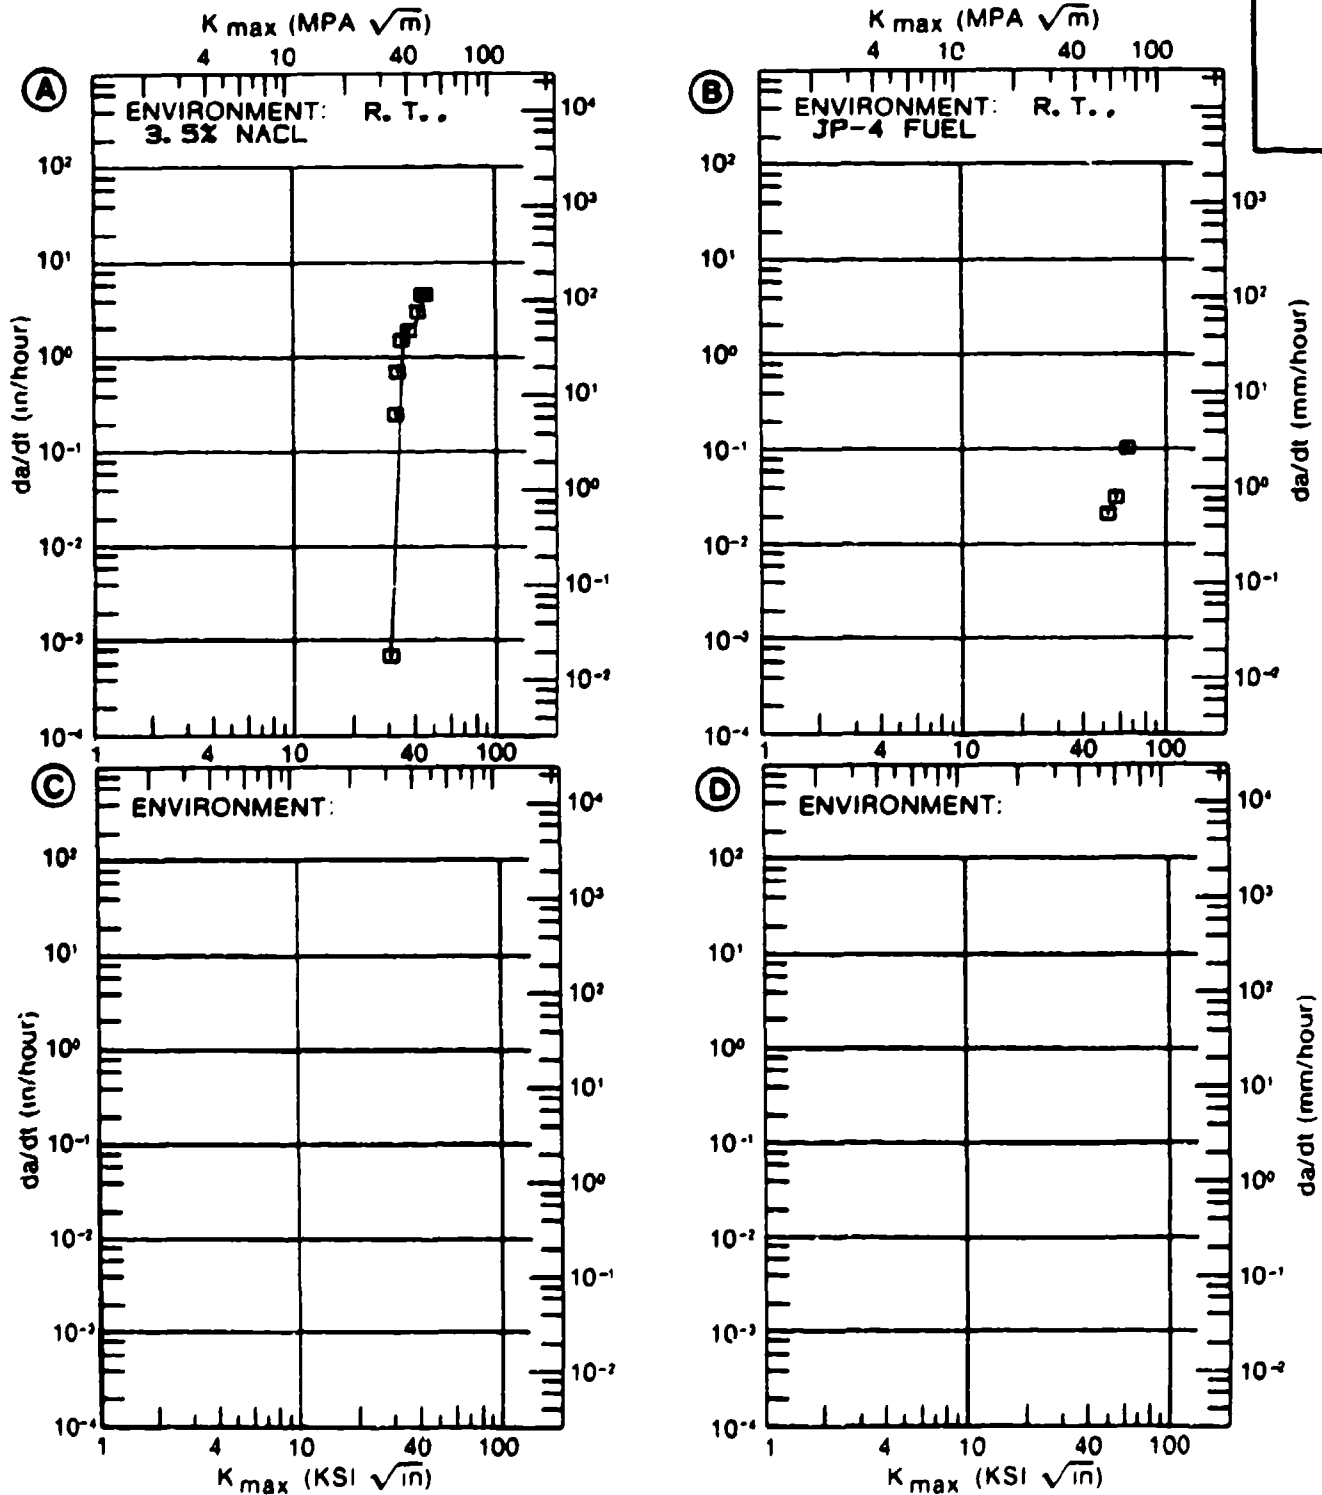


Figure 4.11.3.134

TABLE 4.11.3.135

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.11.3.135 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V			
CONDITION: 1000F 2HR					
K MAX (KSI*IN**1/2)		DA/DT (10**-3 IN/HOUR)			
		A	B	C	D
		E= R. T. 3. 5% NACL	E= R. T. JP-4 FUEL		
K MAX MIN	A:	35.60	222.		
	B:				
	C:				
	D:				
		40.00	3703.		
K MAX MAX	A:	47.00	28832.		
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		46.58	0.00		
PERCENT ERROR					

CONDITION/HT: 1000F 2HR
 FORM: 2.0" TH FORGING
 SPECIMEN TYPE: TDCB
 ORIENTATION: L-T
 YIELD STRENGTH: 145.0 KSI
 ULT. STRENGTH:

SPECIMEN THK: 1.250"
 SPECIMEN WIDTH: 5.500"
 CRACK LENGTH (A₀):
 K_{Isc}: 31.0; 43.0 KSI (SORT IN)
 REFERENCES: 84380

TITAN.
 ALLOY
 TI-6AL-
 4V

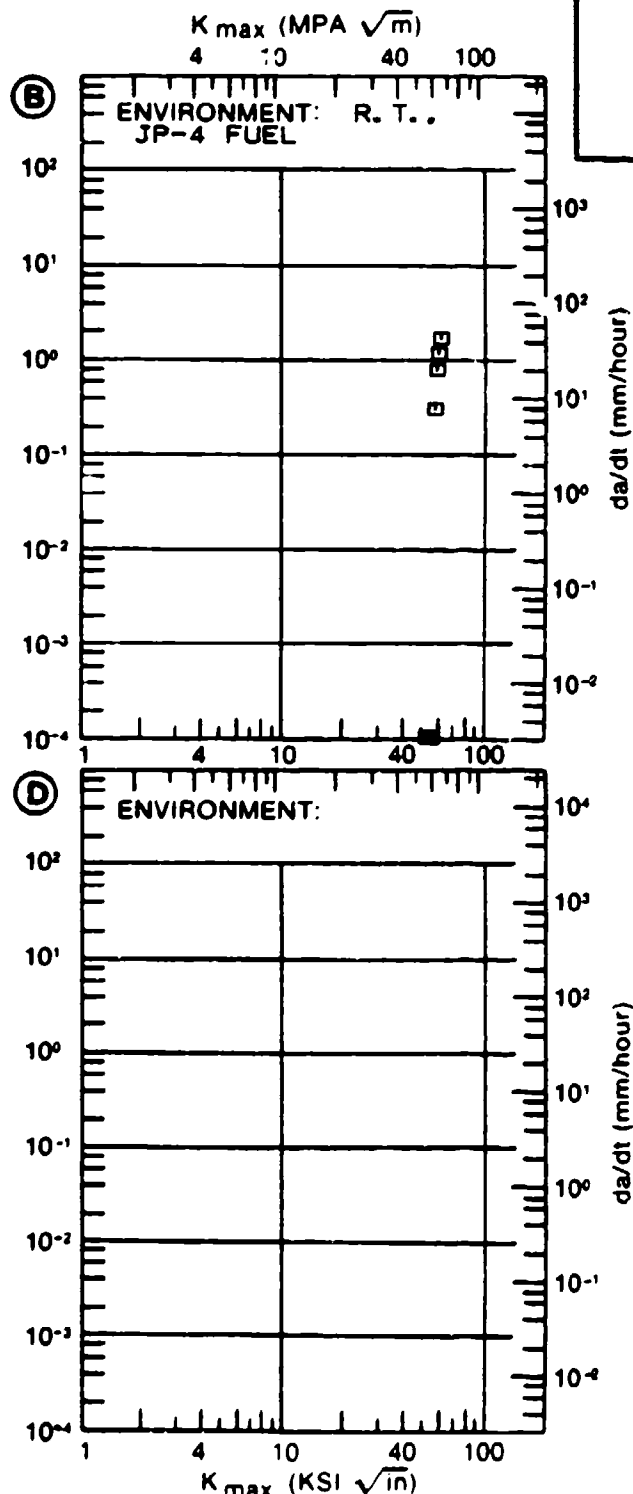
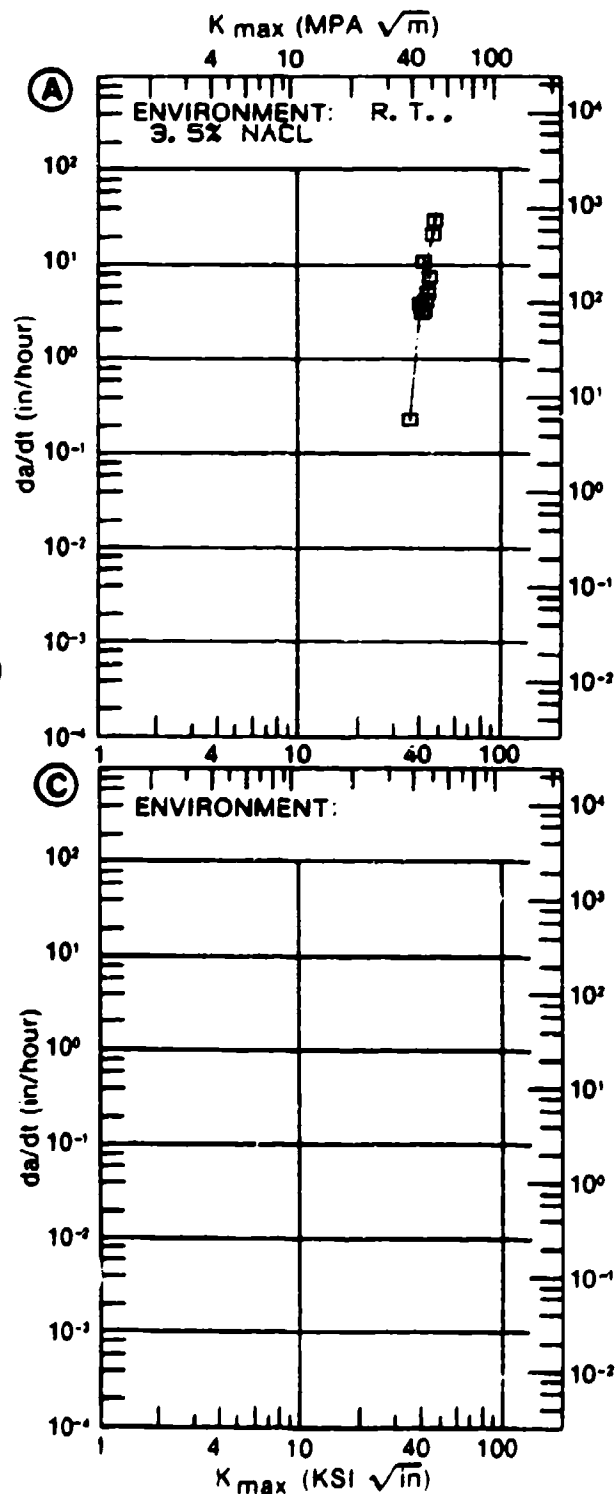


Figure 4.11.3.135

TABLE 4.11.3.136

CONDITION	PROPR T... FORM THICK (IN)	TEST SPEC TEMP OR (F)	YIELD STR (KSI)	ENVIRONMENT	SPECIMEN		WIDTH (IN)	DESIGN (IN)	CRACK LENGTH (IN)	K(I)	K(SORT IN)	MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
					W	B									
		R T	116.0	3.5 PCT NAACL				CANT	115.00		95.00*				1967 70887
		R T	103.0	METHANOL	1.100	0.750	CANT		98.00		60.00*				1968 R4328
		R T	103.0	N-HEXANE	1.100	0.750	CANT		98.00		80.00*				1968 R432E
		R T	103.0	3.5 PCT NAACL	1.100	0.750	CANT		98.00		80.00*				1968 R4328
	1.25	R T	106.0	JP-4 FUEL	3.073	1.249	BMOL	1.365			66.50				>133920 1977 MA005
	1.25		106.0		3.073	1.231	BMOL	1.335			66.60				>133920 1977 MA005
	1.25		108.0		3.078	1.231	BMOL	1.384			69.00				>133920 1977 MA005
	1.25		108.0		3.078	1.252	BMOL	1.363			68.00				>133920 1977 MA005
	1.25	R T	106.0	SIM. SEA WATER	3.077	1.249	BMOL	1.619			69.60				>133920 1977 MA005
	1.25		106.0		3.077	1.230	BMOL	1.369			69.30				>133920 1977 MA005
	1.25		108.0		3.077	1.231	BMOL	1.364			67.70				>133920 1977 MA005
	1.25		108.0		3.073	1.233	BMOL	1.335			68.50				>133920 1977 MA005
ALPHA-BETA FORCED	F	2.25	R T	T-L	144.9	INDUSTRIAL ATM	2.000	1.000	CT		36.50	27.00			1973 R668R
ALPHA-BETA FORCED	F	2.25	R T	T-L	144.9	SEACOAST ATM	2.000	1.000	CT		36.50	18.00			1973 R668R
ALPHA-BETA FORCED	F	2.25	R T	T-L	144.9	3.5 PCT NAACL	2.000	1.000	CT		36.50	27.00			1973 R668R
AS RECEIVED PROBABLY PA	P		R T	T-8	125.0	3.5 PCT NAACL			CANT*		120.00	103.00*			1968 74395
BETA FORCED	F	2.25	R T	T-L	134.9	INDUSTRIAL ATM	2.000	1.000	CT		44.20	42.00			1973 R668R

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(KI/SCC/TYS)SQUARED

TABLE 4.11.3.136 (Con't)

CONDITION	--PRODUCT--		TEST SPEC YIELD		TITANIUM		SPECIMEN		CRACK		MEAN	STAN	TEST	DATE	REFE	
	FORM	THICK	TEMP	OR	STR	ENVIRONMENT	WIDTH	THICK	DESIGN	LENGTH						K(0)
	(IN)	(F)	(KSI)			(IN)	(IN)	(IN)	(IN)	(KSI)	(IN)	(IN)	(MIN)			
BETA FORGED	F	2.25	R.T.	T-L	134.9	SEACOAST ATM	2.000	1.000	CT	----	44.20	42.00	----	1973	B6685	
BETA FORGED	F	2.25	R.T.	T-L	134.9	3.5 PCT NAACL	2.000	1.000	CT	----	44.20	34.00	----	1973	B6680	
FINISH RINLED 1420F	P	3.00	R.T.	T-S	114.0	3.5 PCT NAACL	2.000	0.750	NB	*	1.166	116.00	90.10*	----	1972	B4036
							2.000	0.750	NB	*	1.215	116.00	95.00*	----	1972	B4036
							2.000	0.750	NB	*	0.303	116.00	94.00*	----	1972	B4036
							2.000	0.750	NB	*	1.153	116.00	94.60*	----	1972	B4036
							3.000	1.500	NB	*	1.105	-----	79.60	----	1972	B4036
							3.000	1.500	NB	*	1.051	-----	74.30	----	1972	B4036
							3.000	1.500	NB	*	1.163	-----	87.20	----	1972	B4036
							3.000	1.500	NB	*	1.043	-----	78.60	----	1972	B4036
							3.000	2.000	NB	*	0.920	-----	61.90	----	1972	B4036
							3.000	2.000	NB	*	1.005	-----	78.00	----	1972	B4036
											73.70					
												76.2/			7.8	
GTA - WELD POSTWELD 1100F 2HR (HEAT AFFECTED ZONE)	P	1.25	R.T.	L-T	----	FIELD CLEANING SOLVENT	5.500	0.500	DCB	----	>	48.00	----	1974	B9004	
GTA - WELD POSTWELD 1100F 2HR (HEAT AFFECTED ZONE)	P	1.25	R.T.	L-T	----	S.T.M.	5.500	0.500	DCB	----	>	69.00*	----	1974	B9004	
							5.500	0.750	DCB	----	>	76.00*	----	1974	B9004	
							5.500	1.000	DCB	----	>	58.00	----	1974	B9004	
GTA - WELD POSTWELD 1100F 2HR (HEAT AFFECTED ZONE)	P	1.25	R.T.	L-T	----	SHOP CLEANING SOLVENT	5.500	0.500	DCB	----	>	64.00*	----	1974	B9004	
GTA WELD POSTWELD 1200F 1HR (HEAT AFFECTED ZONE)	P	1.25	R.T.	L-T	----	S.T.M.	5.500	0.125	DCB	----	>	67.00*	----	1974	B9004	

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(KISCC/TYS)SQUARED

TABLE 4.1.1.3.136 (Con't)

CONDITION	- PRODUCT - FORM THICK (IN)	TEST SPEC TEMP (F)	OR STR	YIELD (KSI)	TITANIUM	TI-6AL-4V	K(ISSC)	SPECIMEN		CRACK LENGTH (IN)	K(ISSC)	K(ISSC)	MEAN DEV	STAN DEV	TEST TIME (MIN)	DATE REFER
								WIDTH (IN)	THICK (IN)							
GTA WELD POSTWELD 1400F 1HR (HEAT AFFECTED ZONE)	P 1.25	R.T.	L-T	----	S.T.W.	3.500	0.125	DCB	----	>	62.00*	----	----	----	1974	89004
GTA WELD POSTWELD 1200F 1HR (HEAT AFFECTED ZONE)	P 1.25	R.T.	L-T	----	S.T.W.	3.500	0.250	DCB	----	>	66.00*	----	----	----	1974	89004
GTA WELD POSTWELD 1400F 1HR (HEAT AFFECTED ZONE)	P 1.25	R.T.	L-T	----	S.T.W.	3.500	0.250	DCB	----	>	70.00*	----	----	----	1974	89004
GTA WELD POSTWELD 1100F 2HR (WELD ZONE)	P 1.25	R.T.	L-T	----	S.T.W.	3.500	0.500	DCB	----	----	93.00*	----	----	----	1974	89004
MILL ANNEALED	S 0.13	R.T.	---	----	A-50	1.300	0.125	MOL	----	----	68.00*	----	----	----	1974	88700
MILL ANNEALED	S 0.13	R.T.	---	----	MCB	1.300	0.125	MOL	----	----	38.60*	----	----	----	1974	88700
MILL ANNEALED	S 0.13	R.T.	---	----	MCB/1PCT COR	1.300	0.125	MOL	----	----	40.80*	----	----	----	1974	88700
MILL ANNEALED	S 0.20	R.T.	T-L	----	DIST WATER	----	0.200	DCB	----	----	33.00*	----	----	----	1971	81221
MILL ANNEALED	S 0.20	R.T.	T-L	----	1 M KF	----	0.200	DCB	----	----	35.00*	----	----	----	1971	81221
MILL ANNEALED	S 0.20	R.T.	T-L	----	3 M KF	----	0.200	DCB	----	----	37.00*	----	----	----	1971	81221
MILL ANNEALED	S 0.20	R.T.	T-L	----	6 M KF	----	0.200	DCB	----	----	31.00*	----	----	----	1971	81221
MILL ANNEALED	S 0.20	R.T.	T-L	----	6M KF, 0 MV	----	0.200	DCB	----	----	19.00*	----	----	----	1971	81221
MILL ANNEALED	S 0.20	R.T.	T-L	----	6M KF, +1000RV	----	0.200	DCB	----	----	16.00*	----	----	----	1971	81221
MILL ANNEALED	S 0.20	R.T.	T-L	----	6M KF, +500RV	----	0.200	DCB	----	----	17.00*	----	----	----	1971	81221

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(KI/SCC/TYB)SQUARED

TABLE 4.11.3.136 (Con't)

CONDITION	---PRODUCT--- FORM THICK (IN)	TEST TEMP OR STR (F)	SPEC YIELD (KSI)	ENVIRONMENT	TITANIUM		WIDTH (IN)	THICK (IN)	DESIGN (IN)	CRACK LENGTH (IN)	K (IBCC)	K (ISCC)	K (ISCC) MEAN (KSI*SQRT IN)	STAN DEV	TEST TIME (MIN)	DATE REFER
					TI-6AL-4V	K (IBCC)										
MILL ANNEALED S	0.20	R.T.	T-L	6M KF.-1000HV	0.200	DCB	0.200	DCB	0.200	DCB	31.00*				1971	81221
MILL ANNEALED S	0.20	R.T.	T-L	6M KF.-1500HV	0.200	DCB	0.200	DCB	0.200	DCB	38.00*				1971	81221
MILL ANNEALED S	0.20	R.T.	T-L	6M KF.-3000HV	0.200	DCB	0.200	DCB	0.200	DCB	20.00*				1971	81221
MILL ANNEALED P	0.50	R.T.	L-S	3.5 PCT NaCl	---	NB	---	---	---	---	61.00	32.00			1969	75386
MILL ANNEALED P	1.00	R.T.	T-S	120.0 3.5 PCT NaCl	1.000	0.750	CANT*	---	---	---	88.00	67.00*			1967	70931
MILUTEMAN CASING	P	---	R.T.	T-S	0.750	0.100	CANT	---	---	---	64.00	55.00*			1967	70931
RA	P	1.50	R.T.	L-T	117.0	S.T.M.	5.500	1.000	DCB	---	74.00	60.00*			60300	1976 R1006
		1.50			117.0		5.500	1.000	DCB	---	74.00	> 69.00*			60300	1976 R1006
		1.50			117.0		5.500	1.000	DCB	---	74.00	60.00*			60300	1976 R1006
		1.50			121.0		5.500	1.000	DCB	---	74.00	55.00			54340	1976 R1006
		1.50			121.0		5.500	1.000	DCB	---	76.00	63.00			54360	1976 R1006
		1.50			121.0		5.500	1.000	DCB	---	76.00	> 67.00			51750	1976 R1006
		1.50			121.0		5.500	1.000	DCB	---	76.00	> 69.00			54360	1976 R1006
		2.50			122.0		5.500	1.000	DCB	---	77.00	56.00			70140	1976 R1006
		2.50			122.0		5.500	1.000	DCB	---	77.00	59.00			70140	1976 R1006
		2.50			122.0		5.500	1.000	DCB	---	77.00	60.00			54340	1976 R1006
		2.50			122.0		5.500	1.000	DCB	---	77.00	60.00			54360	1976 R1006
RA	P	1.50	R.T.	T-L	122.0	F.C.S.	5.500	1.000	DCB	---	77.00	70.00			119100	1976 R1006
RA	P	1.50	R.T.	T-L	122.0	B.C.S.	5.500	1.000	DCB	---	77.00	75.00			59100	1976 R1006
		1.50			122.0		5.500	1.000	DCB	---	77.00	63.00			112200	1976 R1006
RA	P	1.50	R.T.	T-L	122.0	S.T.M.	5.500	1.000	DCB	---	77.00	61.00			60300	1976 R1006
		1.50			122.0		5.500	1.000	DCB	---	77.00	62.00			54360	1976 R1006
		1.50			122.0		5.500	1.000	DCB	---	77.00	58.00			60300	1976 R1006

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5 (KIBCC/TYS) SQUARED

TABLE 4.11.3.136 (Con't)

CONDITION	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR STR (KSI)	YIELD	TITANIUM	TI-6AL-4V	K (KISCC)	SPECIMEN		CRACK LENGTH (IN)	K (KISCC)	MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER	
							WIDTH (IN)	THICK (IN)							
RA	P	1.50	R.T.	F-L	122.0	S.T.M.	5.500	1.000	DCB	77.00	62.00		60300	1976	R1006
		2.00			126.0		5.500	1.000	DCB	80.00	61.00		61980	1976	R1006
		2.00			126.0		5.500	1.000	DCB	80.00	59.00	59.8/	61980	1976	R1006
RA	F	4.00	R.T.	I-L	119.0	S.T.M.	5.500	1.000	DCB	79.00	59.00		60360	1976	R1006
		4.00			119.0		5.500	1.000	DCB	79.00	51.00	53.0/	60360	1976	R1006
RA	F		R.T.	S-L		S.T.M.	5.500	1.000	DCB	78.00	> 57.00		64920	1976	R1006
							5.500	1.000	DCB	79.00	56.00		60180	1976	R1006
							5.500	1.000	DCB	79.00	56.00		60660	1976	R1006
							5.500	1.000	DCB	78.00	> 71.00		60660	1976	R1006
		4.00			129.0		5.500	1.000	DCB	79.00	59.00		64920	1976	R1006
		4.00			129.0		5.500	1.000	DCB	79.00	57.00	56.0/	61680	1976	R1006
SOL TREATED 1050F 4HR. W/CLDED 1050H 4HR	F		85		133.0	N204 315PSIG	1.500	0.062	PTSC	0.026	47.00	32.00*		1969	78535
					139.0		1.500	0.062	PTSC	0.026	47.00	31.00*		1969	78535
SOL TREATED 1050F 4+4 HR	F		85		160.0	N204 315PSIG	1.000	0.092	PTSC	0.018	49.00	28.00*		1969	78535
					161.0		1.000	0.092	PTSC	0.018	49.00	30.00*		1969	78535
1300F 2HR AC	E	0.50	R.T.	L-S	121.2	3.5 PCT NAACL	1.500	0.480	NB		94.70	65.00*		1972	84282
1300F 2HR AC	E	0.50	R.T.	L-T	128.9	3.5 PCT NAACL	1.500	0.480	NB		83.30	73.00*		1972	84282
1700F 4HR FC TO 1400F AC. DIFFUSION BOND THERMAL CYCLE	F	1.50	R.T.	L-T		S.T.M.	5.500	1.000	DCB			66.00		1974	89004
1700F 4HR FC TO 1400F AC. DIFFUSION BOND THERMAL CYCLE	F	1.50	R.T.	T-L		FIELD CLEANING SILVENT	5.500	1.000	DCB		94.00	70.00		1974	89004

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.3(KISCC/TYS)SQUARED

TABLE 4.11.3.136 (Con't)

CONDITION	-- PRODUCT --		TEST SPEC		YIELD STR (KG)	ENVIRONMENT	TITANIUM		WIDTH (IN)	SPECIMEN		CRACK LENGTH (IN)	K (ISCC)	MEAN (KSI*SQRT IN)	STAN DEV	TEST TIME (MIN)	DATE REFER
	FORM	THICK (IN)	THICK (IN)	TEMP (F)			T--L	TI-6AL-4V		K (ISCC)	THICK (IN)						
1700F 4HR FC TO 1400F AC, DIFFUSION BOND THERMAL CYCLE	P	1.50	R.T.	T--L	---	S.T.W.	---	5.500	1.000	DCB	---	---	60.00	---	---	1974 07004	
		1.00			---		---	5.500	1.000	DCB	---	92.00	44.00	---	---	1974 07004	
		2.00			---		---	5.500	1.000	DCB	---	94.00	61.00	---	---	1974 07004	
		2.00			---		---	5.500	1.000	DCB	---	92.00	53.00	---	---	1974 07004	
		2.00			---		---	5.500	1.000	DCB	---	92.00	58.00	---	---	1974 07004	
					---		---				---			35.2/	7.0		
1700F 4HR FC TO 1400F AC, DIFFUSION BOND THERMAL CYCLE	P	1.50	R.T.	T--L	---	SHOP CLEANING SOLVENT	---	5.500	1.000	DCB	---	94.00	69.00	---	---	1974 07004	
1725F 1HR WQ 1250F 4HR AC (STA)	E	0.50	R.T.	L-S	139.4	3.5 PCT NaCl	---	1.500	0.480	NB	---	77.80	60.00	---	---	1972 04202	
		0.50			140.3		---	1.500	0.480	NB	---	74.90	70.00*	---	---	1972 04202	
1750F 1HR WQ 1000F 1HR AC (STA)	E	0.50	R.T.	L-S	145.7	3.5 PCT NaCl	---	1.500	0.480	NB	---	67.20	51.00	---	---	1972 04202	
		0.50			146.9		---	1.500	0.480	NB	---	65.80	46.00	---	---	1972 04202	
							---				---			48.5/	3.5		
1750F WQ 1000F F BHP 1000F (ALPHA+BETA)	F	0.50	R.T.	---	160.0	DIST WATER +50	---	1.000	0.030	PTSC	---	43.90	40.00*	---	>	1080 1968 77290	
1750F WQ 1000F F BHP 1000F (ALPHA+BETA)	F	0.50	R.T.	---	160.0	METHANOL	---	1.000	0.030	PTSC	---	43.90	< 26.00*	---	---	180 1968 77290	
		0.50			160.0		---	1.000	0.060	PTSC	---	45.90	> 26.00*	---	---	180 1968 77290	
1750F WQ 1000F F BHP 1000F (ALPHA+BETA)	F	0.50	R.T.	---	160.0	PPH NA2CR207	---	1.000	0.060	PTSC	---	43.90	43.00*	---	>	1080 1968 77290	
1750F 1.5HR WQ F 1000F-1100F BHP. 950F 0HR	F	---	R.T.	---	160.9	AERDZINE 50	---	0.800	0.095	PTSC	---	52.20	37.00*	---	---	1969 75528	
					161.4		---	0.800	0.095	PTSC	---	51.90	38.00*	---	---	1969 75528	

*NOTE: DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5 (KISCC/TYS) SQUARED

TABLE 4.11.3.136 (Con't)

CONDITION	TITANIUM		TEST SPEC OR STR (KSI)	YIELD	ENVIRONMENT	WIDTH (IN)	SPECIMEN		CRACK LENGTH (IN)	K (ISCC)	MEAN	DEV	TEST TIME (MIN)	DATE REFER		
	FORM	THICK (IN)					THICK (IN)	DESIGN							K (G)	K (ISCC)
1750F 1 SHR WQ F 1050F-1100F ENR, 950F ENR			R. T.	161.4 160.9	FREON TF	0.800 0.800	0.095 0.095	PTSC PTSC	51.50 52.20	42.00* 39.00*			1969 75528 1969 75528			
1750F 1 SHR WQ F 1050F-1100F ENR, 950F ENR			R. T.	160.9 161.4	MS04	0.800 0.800	0.095 0.095	PTSC PTSC	52.20 51.50	40.00* 41.00*			1969 75528 1969 75528			
1750F 1000F ENR AC	F	2.30	R. T.	144.9	JP-4 FUEL	5.000	1.250	TDCB	50.90	43.30			1971 84360			
1750F 1000F ENR AC	F	2.30	R. T.	144.9	3.5 PCT NAACL	5.000	1.250	TDCB	50.90	31.00			1971 84360			
1790F 1 SHR WQ S 1160F ENR + 1025F ENR AC		1.33	R. T.		MARTIN MARIETTA REFINED GRADE HYDRAZINE	1.300	0.125	WOL		46.20*			1974 88700			
1790F 1 SHR WQ S 1160F ENR + 1025F ENR AC		1.33	R. T.		PROPELLANT GRADE HYDRAZINE	1.300	0.125	WOL		64.30*			1974 88700			

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(KISCC/TYS)SQUARED

TABLE 4.12.1.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI 6AL-4V(ELI)

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT LAB AIR AT R.T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
ANNEALED	FORSIMS	0 10	1.00-10.00		12.9 206
RA	PLATE	0 10			10.8

TABLE 4.12.1.1.3
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM T1-6AL-4V (ELI)

TEST CONDITIONS

SPECIMEN ORIENTATION: T-L

ENVIRONMENT: DRY AIR
 AT R.T.

CONDITION/MT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)						
					2	5	10	20	50	100	
BA	PLATE	0.00	15.00					4.02			
BA	PLATE	0.10	1.00						12.8		
BA	PLATE	0.50	0.10-1.00							1.12	
BA	PLATE	0.80	1.00								

TABLE 4.12.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V(E11)

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT LAB AIR AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 3 5 10 20 50 100	
ANNEALED	FORGING	0 10	1 00-50 00		11.9 171
RA	PLATE	0 10	1 00-10 00		7.75 240

TABLE 4.12.1.5

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V (ELI)

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: 100 SATURATED JP-4 FUEL AT R.T.

CONDITION/MT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
BA	PLATE	0.00	15.00		5.14
BA	PLATE	0.10	0.10		123
BA	PLATE	0.10	1.00		106
BA	PLATE	0.50	1.00		13.8
BA	PLATE	0.50	0.10		13.9

TABLE 4.12.1.6
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-4V (ELI)

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: DIST WATER
 AT R. T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS:		FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)						
				(KSI SQRT(IN))	(MPA SQRT(IN))	2.5	5	10	20	50	100	
BA	PLATE	0.00	15.00									9.20
BA	PLATE	0.10	1.00									141
BA	PLATE	0.50	1.00					0.27	13.7			

TABLE 4.12.1.7
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM TI-6AL-4V (ELI)

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: 3.5% NaCl
 AT R. T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
BA	PLATE	0.00	15.00					14.5			
BA	PLATE	0.10	0.10						393		
BA	PLATE	0.10	1.00						214		
BA	PLATE	0.50	1.00					31.3			
BA	PLATE	0.50	0.10					15.0			

TABLE 4.12.1.8

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
TITANIUM Ti-6Al-4V (ELI)

TEST CONDITIONS		ENVIRONMENT		S T W		FATIGUE CRACK GROWTH RATES:							
SPECIMEN ORIENTATION	T-L			AT R. T.		DELTA K LEVELS:	(MSI SQRT(IN))	2	5	10	20	50	100
CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)										
BA	PLATE	0.10	1.00										214
BA	PLATE	0.50	0.10										12.7
BA	PLATE	0.50	1.00							1.13	28.2		

TABLE 4.12.2.1

CONDITION	TITANIUM										K(IIC) STAN DEV	DATE	REFER
	--PRODUCT-- FORM	TEST THICK (IN)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	SPECIMEN-----		CRACK LENGTH (IN)	2.9 (IN)	K(IIC)/TYS**2 (IN)	K(IIC) MEAN (KSI*SQRT IN)			
					WIDTH (IN)	THICK (IN)							
ANNEALED	F	3 00	R T	L-T	117 0	4 000	2 005	CT	2 170	1 24	82 42	1976	MC001
		3 00			117 0	3 926	2 001	CT	2 136	1 31	84 91	1976	MC001
		3 00			117 0	3 996	2 005	CT	2 143	1 26	83 21	1976	MC001
ANNEALED	F	3 00	R T	1-L	117 0	3 997	2 023	CT	2 157	1 31	84 71	1976	MC001
		3 00			117 0	3 991	2 005	CT	2 126	1 29	84 23	1976	MC001
		3 00			117 0	3 995	2 020	CT	2 146	1 28	83 69	1976	MC001
RECRYSTALLIZE ANNEAL	P	3 00	R T	L-T	119 0	4 000	2 000	CT	2 072	0 94	73 32	1976	MC001
		3 00			119 0	4 000	2 000	CT	2 088	1 14	80 66	1976	MC001
		3 00			119 0	4 000	1 999	CT	2 117	0 97	74 26	1976	MC001
RECRYSTALLIZE ANNEAL	P	3 00	R T	T-1	122 0	4 000	2 000	CT	2 059	0 97	76 19	1976	MC001
		3 00			122 0	4 000	2 000	CT	2 034	1 01	77 61	1976	MC001
		3 00			122 0	4 000	2 000	CT	2 102	0 98	76 61	1976	MC001

TABLE 4.12.2.2

TITANIUM		TI-6AL-4V (ELI) K1C																
CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST TEMP (F)	OR	SPEC YIELD STR (KSI)	---SPECIMEN---		CRACK LENGTH CROSS STRESS				K(IAPP) MEAN (KSI*SQRT IN)	STAN DEV	K(I C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER	
						WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)	UNSET (KSI)	MAX (KSI)							R(D)
UNREPEATED	S	0.03	R	T	L-T	136.0	2.000	0.025	0.490	0.780	---	104.00	94.77*	127.27*		1964	60378	
		0.03				136.0	2.000	0.025	0.480	0.800	---	104.00	93.63*	129.62*		1964	60378	
		0.03				136.0	2.000	0.025	0.470	0.750	---	107.00	95.20*	127.37*		1964	60378	
		0.03				136.0	2.000	0.025	0.480	0.750	---	104.00	93.63*	123.79*		1964	60378	
UNREPEATED	S	0.03	R	T	L-T	136.0	2.000	0.025	0.480	0.700	---	105.00	94.53*	119.24*		1964	60378	
		0.03				136.0	4.000	0.025	1.270	1.600	---	71.80	108.22	126.53*		1964	60378	
		0.03				136.0	4.000	0.025	1.280	1.700	---	68.50	103.76	126.31*		1964	60378	
		0.03				136.0	4.000	0.025	1.260	1.650	---	70.60	105.88	127.29*		1964	60378	
UNREPEATED	S	0.03	R	T	L-T	136.0	4.040	0.025	1.270	1.550	---	73.60	110.82	125.44*		1964	60378	
		0.03				136.0	4.040	0.025	1.270	1.650	---	74.90	112.74*107.2/	134.72*	---	1964	60378	
		0.03	R	T	L-T	136.0	17.980	0.025	3.490	6.190	---	49.50	154.33	164.70		1964	60378	
		0.03				136.0	17.980	0.025	3.490	7.610	---	42.10	131.26	164.08		1964	60378	
UNREPEATED	S	0.03	R	T	L-T	136.0	18.000	0.024	3.480	7.350	---	44.10	137.33	167.42		1964	60378	
		0.03				136.0	18.000	0.025	3.900	6.980	---	41.60	129.83	152.10		1964	60378	
	S	0.03	R	T	L-T	136.0	18.000	0.025	3.490	7.350	---	41.60	129.68	136.9/10.3	161.6/	6.5	1964	60378

*NOTE - NPT SECTION STRESS EXCEEDS BOX OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 4.12.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: ANNEALED

TI-6AL-4V (ELI)

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K MIN	A:	12.87	2.61		
	B:				
	C:				
	D:				
		13.00	2.73		
		16.00	6.36		
		20.00	12.9		
		25.00	23.5		
		30.00	37.6		
		35.00	57.6		
	40.00	87.5			
	50.00	206.			
	60.00	506.			
DELTA K MAX	A:	67.30	1005.		
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		6.38			
PERCENT ERROR					

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	
RATIO	0.8-1.25	2
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: ANNEALED
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 1.00- 10.00 HZ

YIELD STRENGTH: 116.8 KSI
 ULT. STRENGTH: 126.7 KSI
 SPECIMEN THK: 0.991- 1.014"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: NC002

TITAN.
 ALLOY
 TI-6AL-
 4V (ELI)

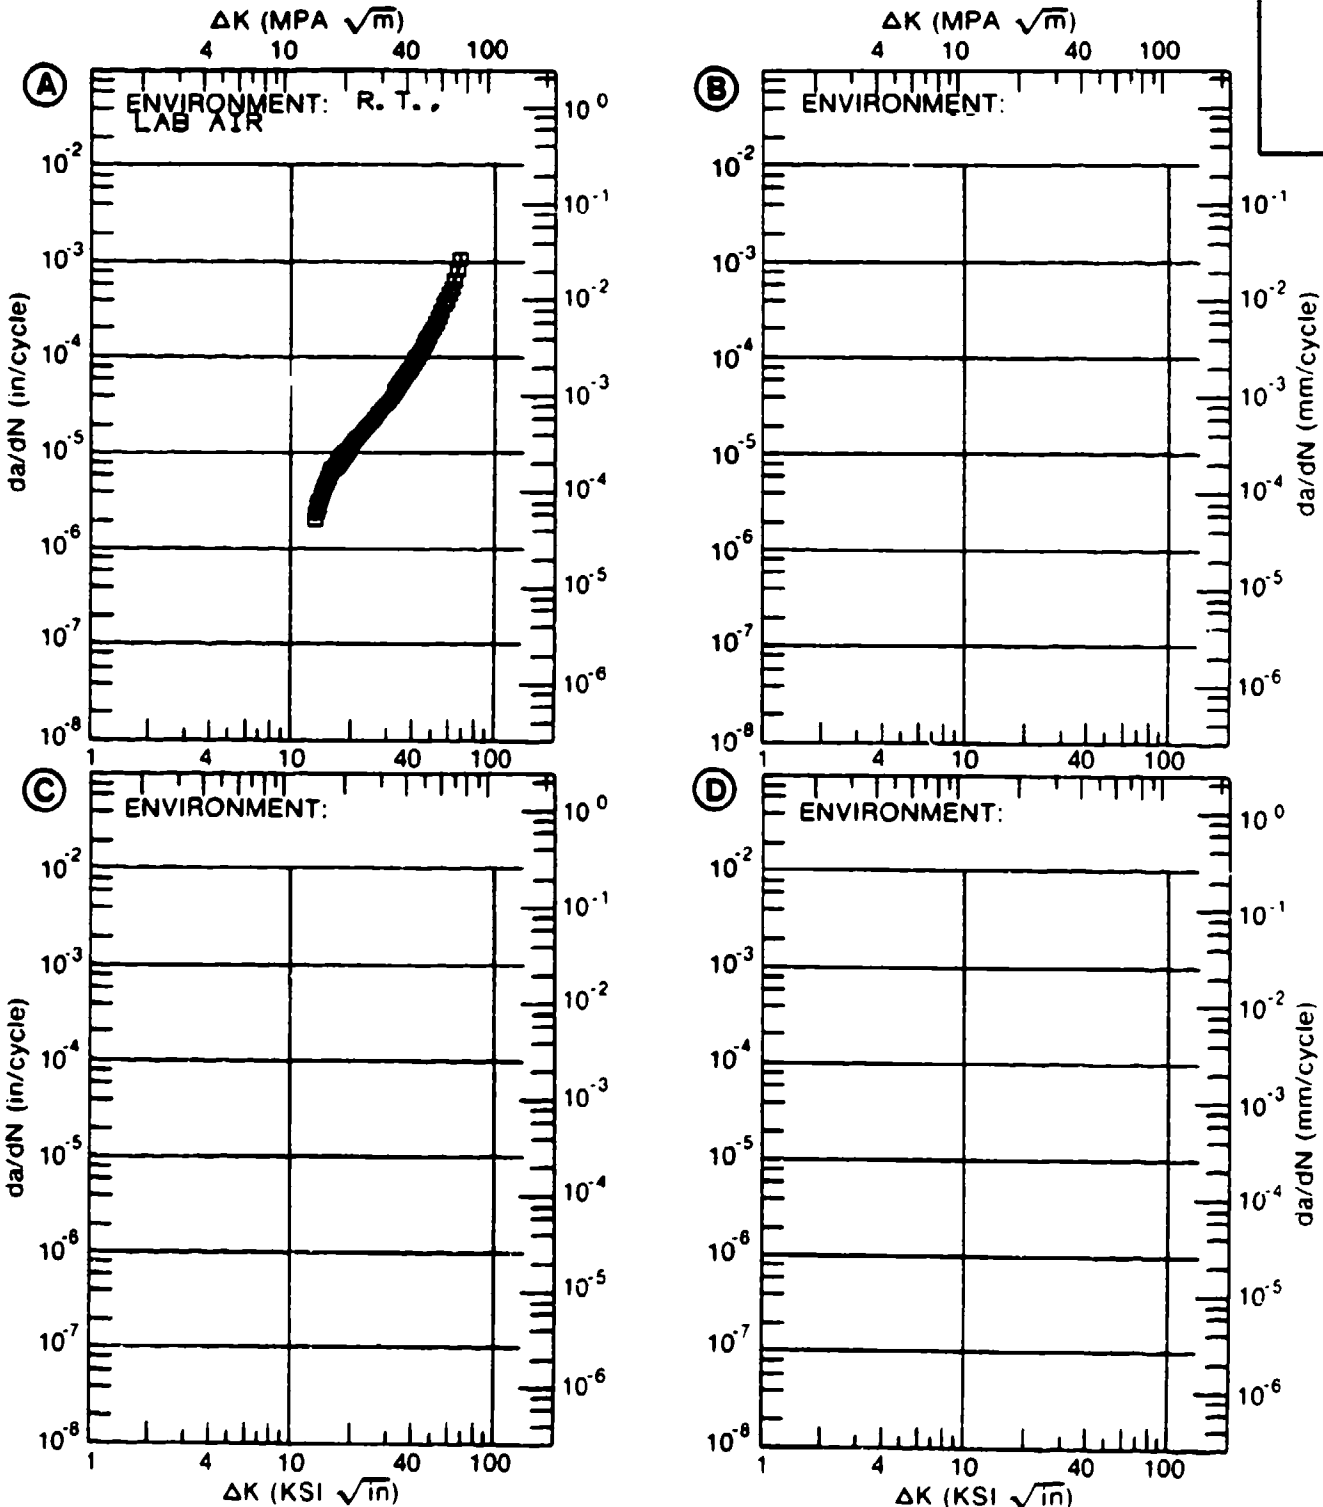


Figure 4.12.3.1

TABLE 4.12.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: ANNEALED					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K	A: 12.55	.717			
MIN	B:				
	C:				
	D:				
	13.00	.974			
	16.00	4.18			
	20.00	11.9			
	25.00	23.6			
	30.00	36.4			
	35.00	52.3			
	40.00	75.1			
	50.00	171.			
	60.00	461.			
DELTA K	A: 63.28	662.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		26.42			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2			
SUMMARY	1.25-2.0	1			
(NP/NA)	>2.0				

CONDITION/HT: ANNEALED
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 1.00- 20.00 HZ

YIELD STRENGTH: 116.9 KSI
 ULT. STRENGTH: 127.0 KSI
 SPECIMEN THK: 0.999- 1.002"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: NC002

TITAN.
 ALLOY

TI-6AL-
 4V (ELI)

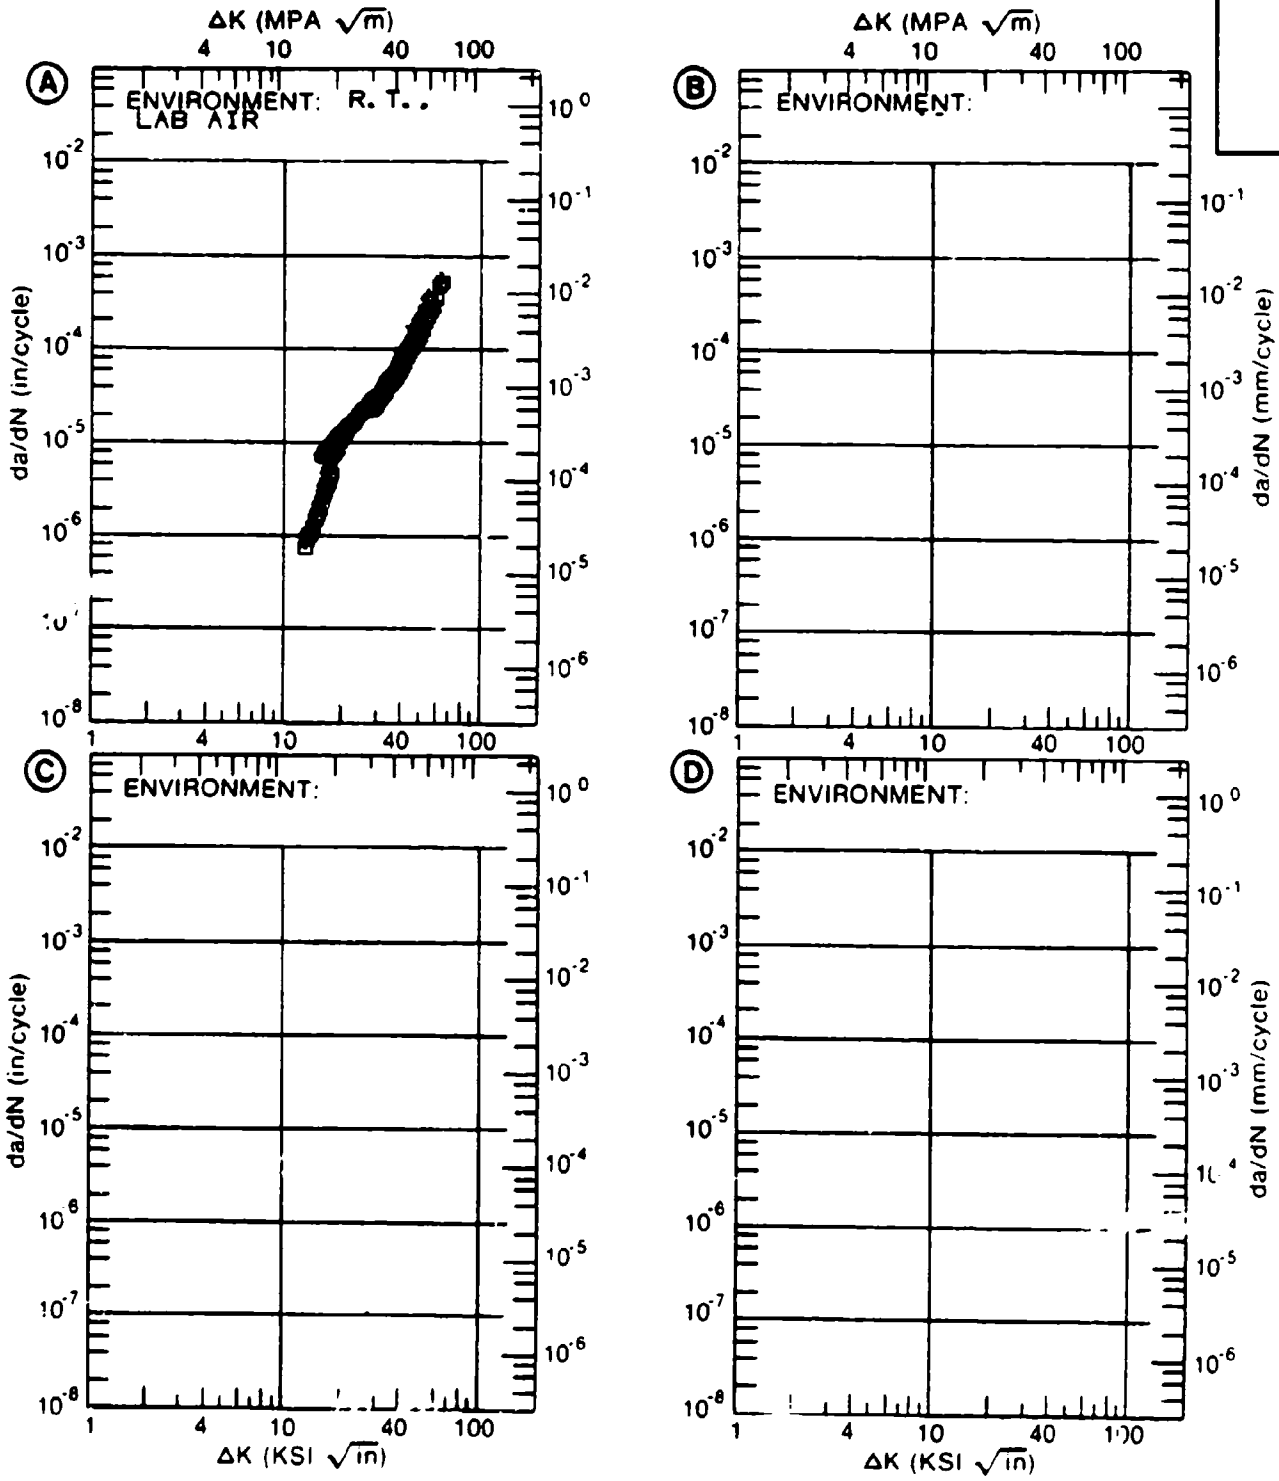


Figure 4.12.3.2

TABLE 4.12.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.3 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: BA					
ENVIRONMENT: R. T. , DRY AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 80		
DELTA K	A: 40. 32	58. 0			
MIN	B: 7. 50		. 190		
	C:				
	D:				
	8. 00		. 286		
	9. 00		. 597		
	10. 00		1. 12		
	13. 00		4. 50		
	16. 00				
	20. 00				
	25. 00				
	30. 00				
	35. 00				
	40. 00				
	50. 00	128.			
	60. 00	229.			
	70. 00	401.			
DELTA K	A: 71. 02	426.			
MAX	B: 13. 61		5. 54		
	C:				
	D:				
ROOT MEAN SQUARE		4. 60	10. 38		
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25				
SUMMARY	1. 25-2. 0				
(NP/NA)	>2. 0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., DRY AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 98140

TITAN. ALLOY
TI-6AL- 4V (ELI)

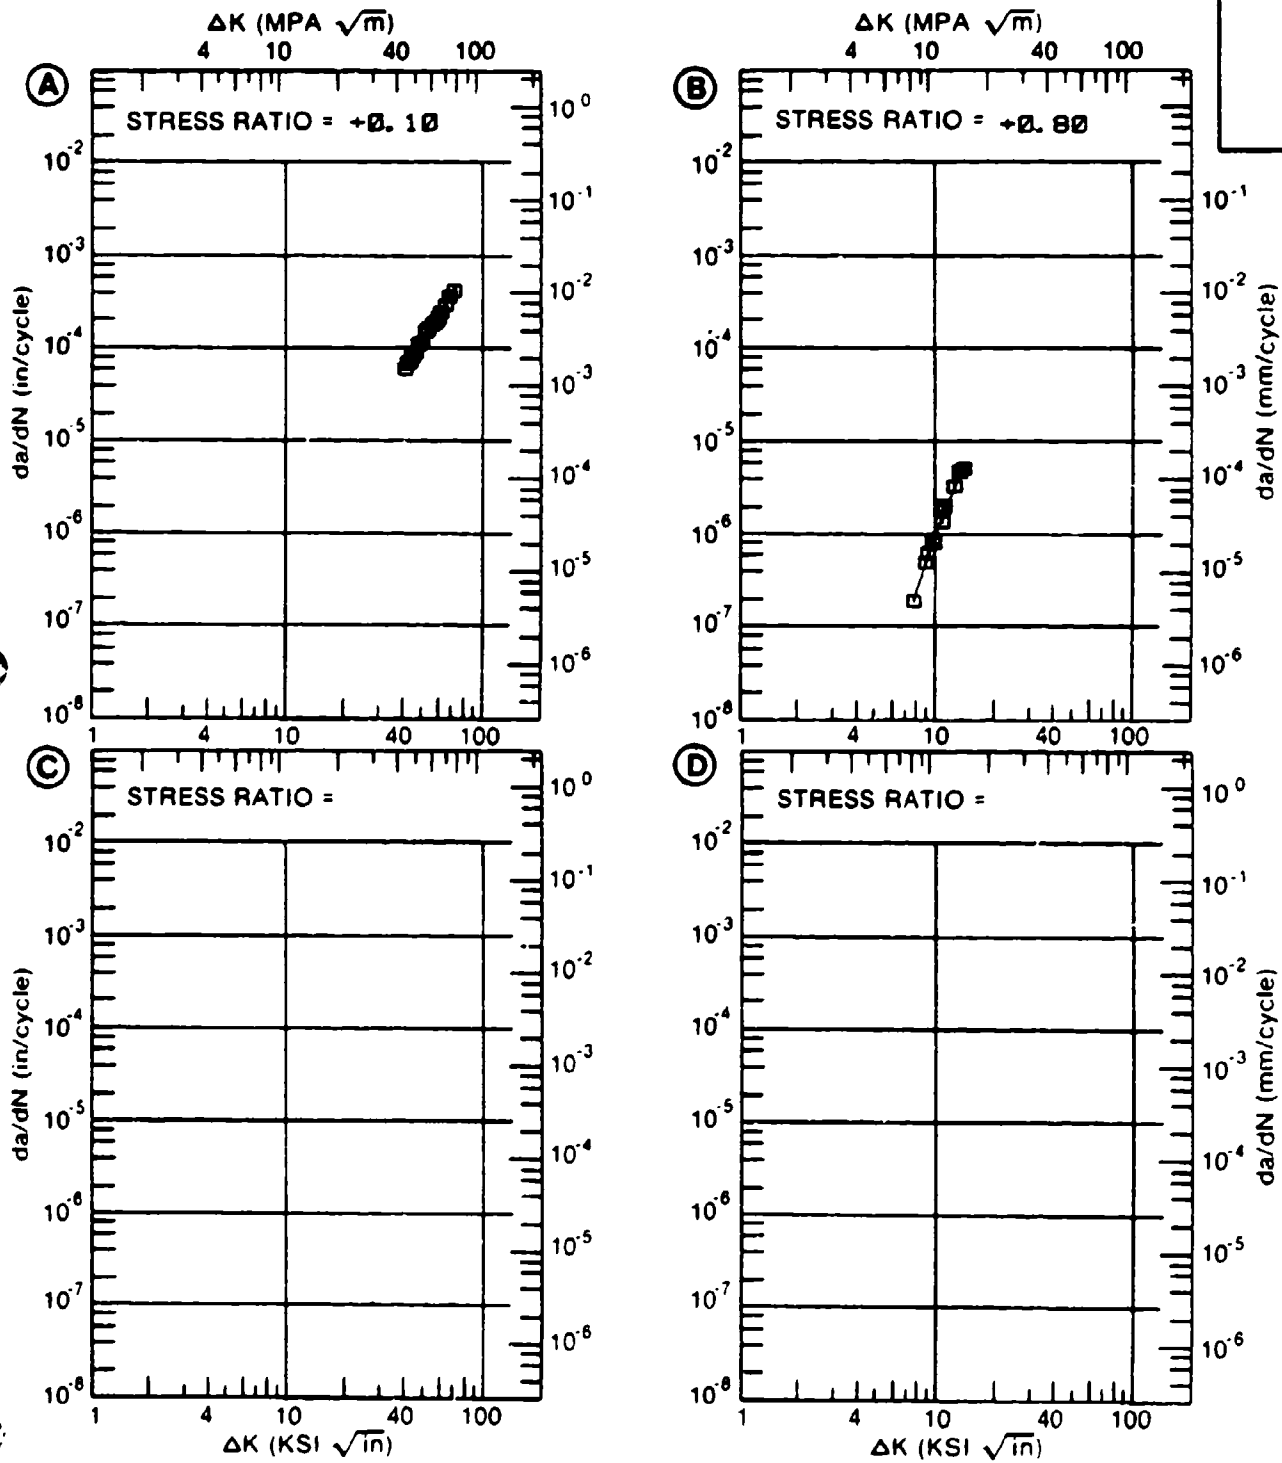


Figure 4.12.3.3

TABLE 4.12.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.4 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-4V (ELI)
CONDITION: BA
ENVIRONMENT: R. T. , 3. 5% NaCl

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	R=+0. 80			
DELTA K A: MIN B: C: D:				
200. 00				
DELTA K A: MAX B: C: D:				

ROOT MEAN SQUARE 0. 00
PERCENT ERROR

LIFE 0. 0-0. 5
PREDICTION 0. 5-0. 8
RATIO 0. 8-1. 25
SUMMARY 1. 25-2. 0
(NP/NA) >2. 0

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 88140

TITAN.
 ALLOY
 TI-6AL-4V (ELI)

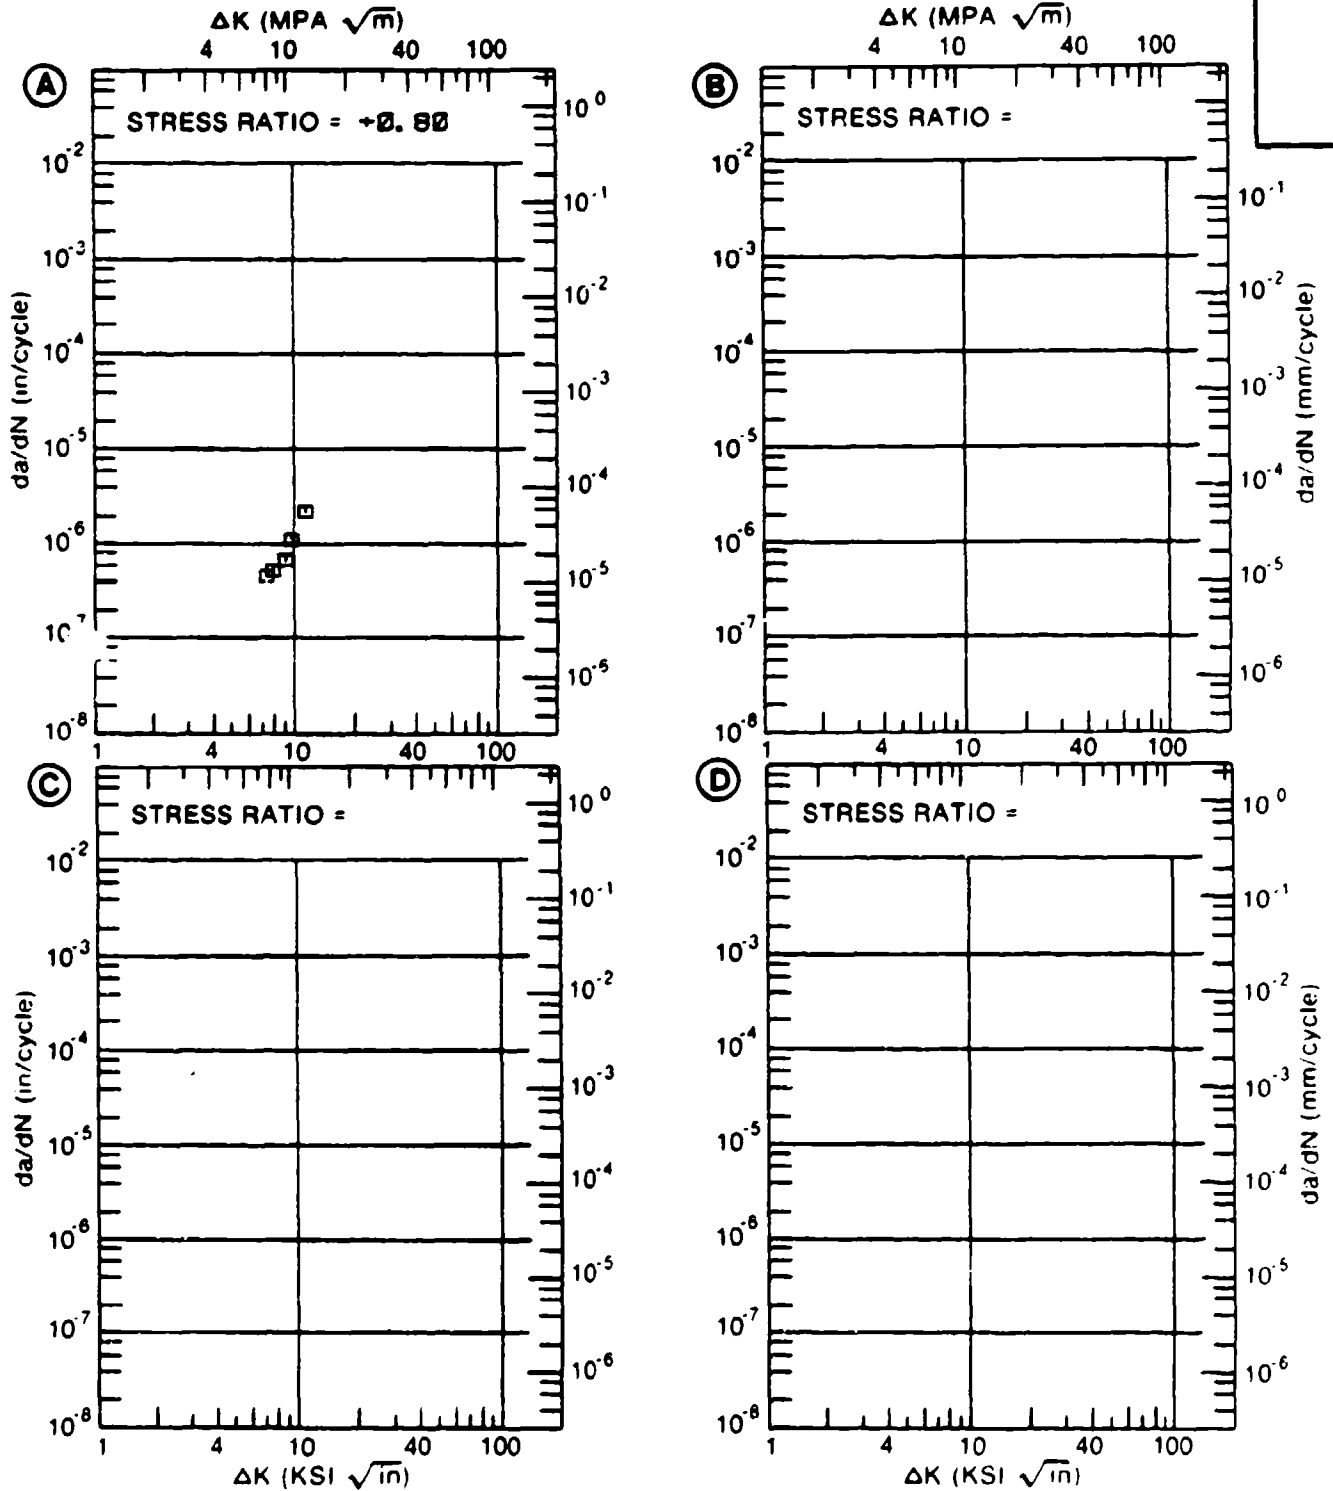


Figure 4.12.3.4

TABLE 4.12.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.5 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM TI-6AL-4V (ELI)
CONDITION: BA

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E= R. T. DRY AIR			
DELTA K A: 11.53	.0879			
MIN B:				
C:				
D:				
13.00	.227			
16.00	1.01			
20.00	4.02			
25.00	11.9			
30.00	22.4			
35.00	31.3			
DELTA K A: 37.95	34.5			
MAX B:				
C:				
D:				

ROOT MEAN SQUARE 24.63
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.00
 FREQUENCY: 15.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 88140

TITAN.
 ALLOY

TI-6AL-4V (ELI)

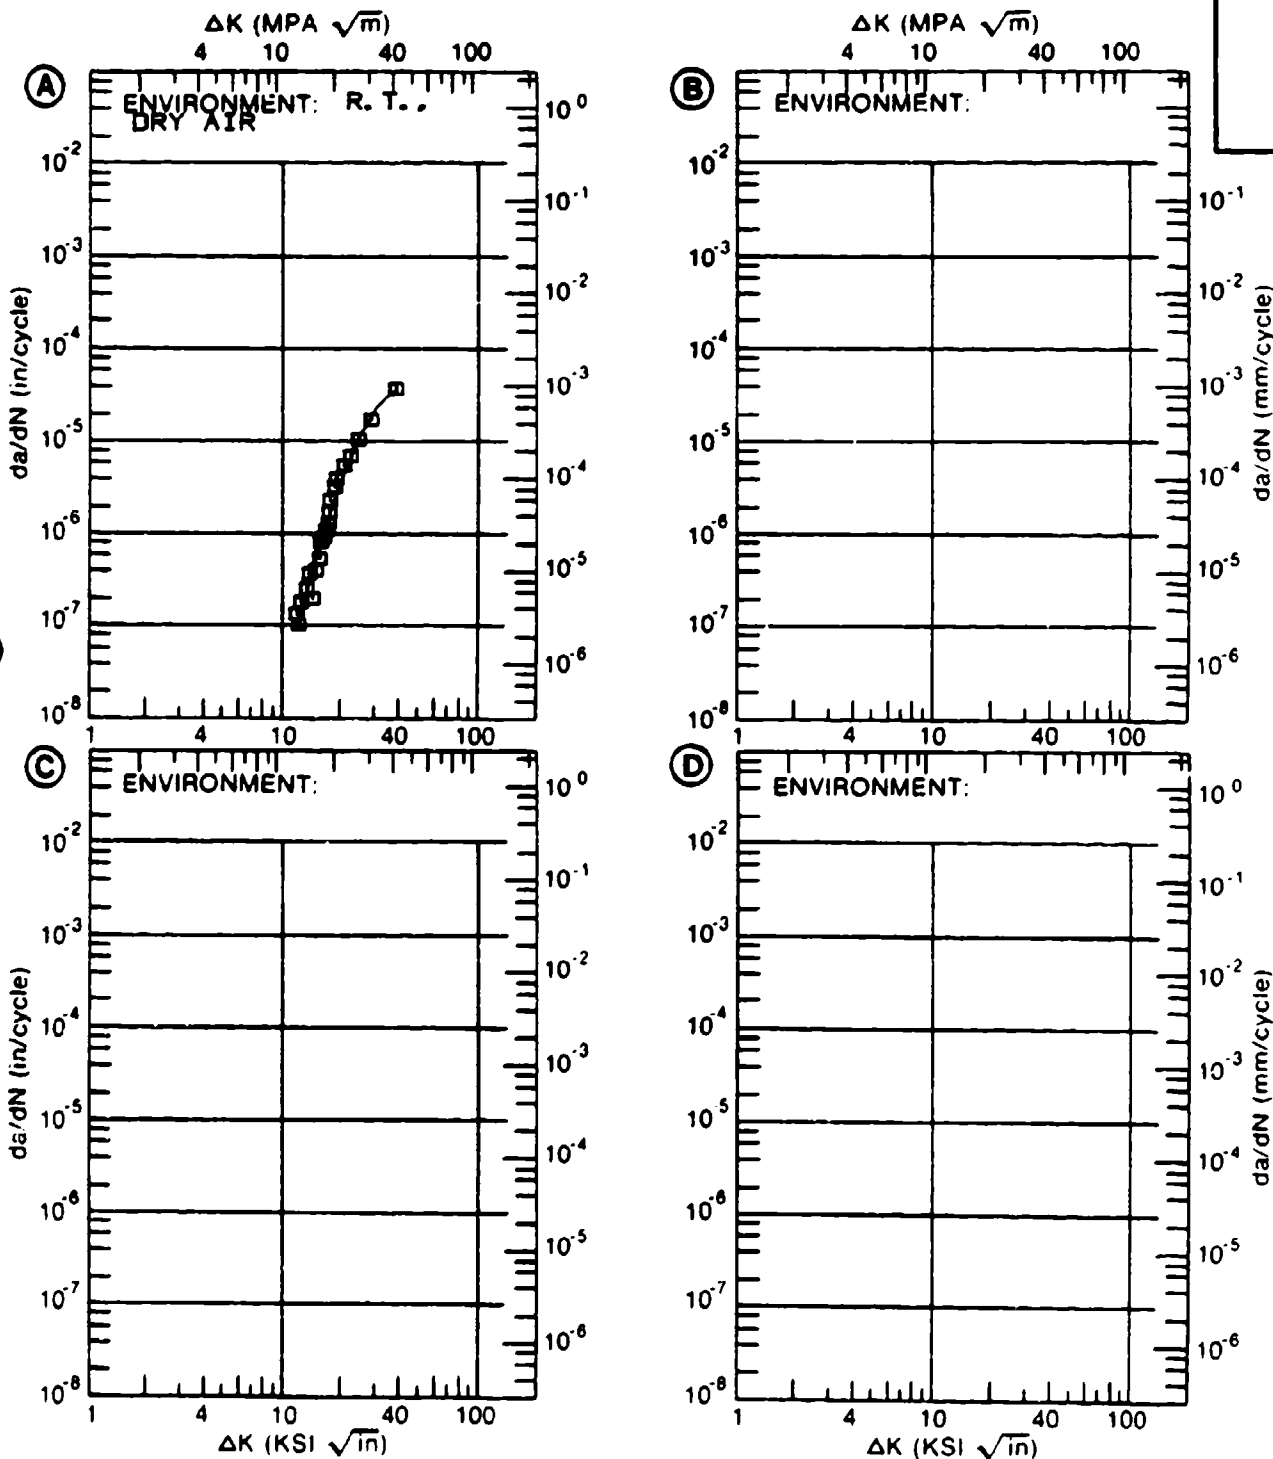


Figure 4.12.3.5

TABLE 4.12.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.6 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. H2O SATURATED JP-4 FUEL	E= R. T. DIST. WATER	E= R. T. 3.5% NaCl	E= R. T. S. T. W.
DELTA K MIN	A: 14.45	.387			
	B: 15.47		.968		
	C: 10.07			.117	
	D: 13.53				.400
	13.00			1.36	
	16.00	1.06	1.27	2.99	1.64
	20.00	5.14	5.20	14.5	
	25.00	13.4	13.0		
	30.00	22.4	22.8		
	35.00	32.4	35.7		
40.00	45.9	55.4			
DELTA K MAX	A: 43.49	59.6			
	B: 40.10		55.9		
	C: 24.47			24.0	
	D: 16.98				3.23
ROOT MEAN SQUARE		11.94	19.22	22.82	17.58
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.00
 FREQUENCY: 15.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 88140

TITAN.
 ALLOY
 TI-6AL-4V (ELI)

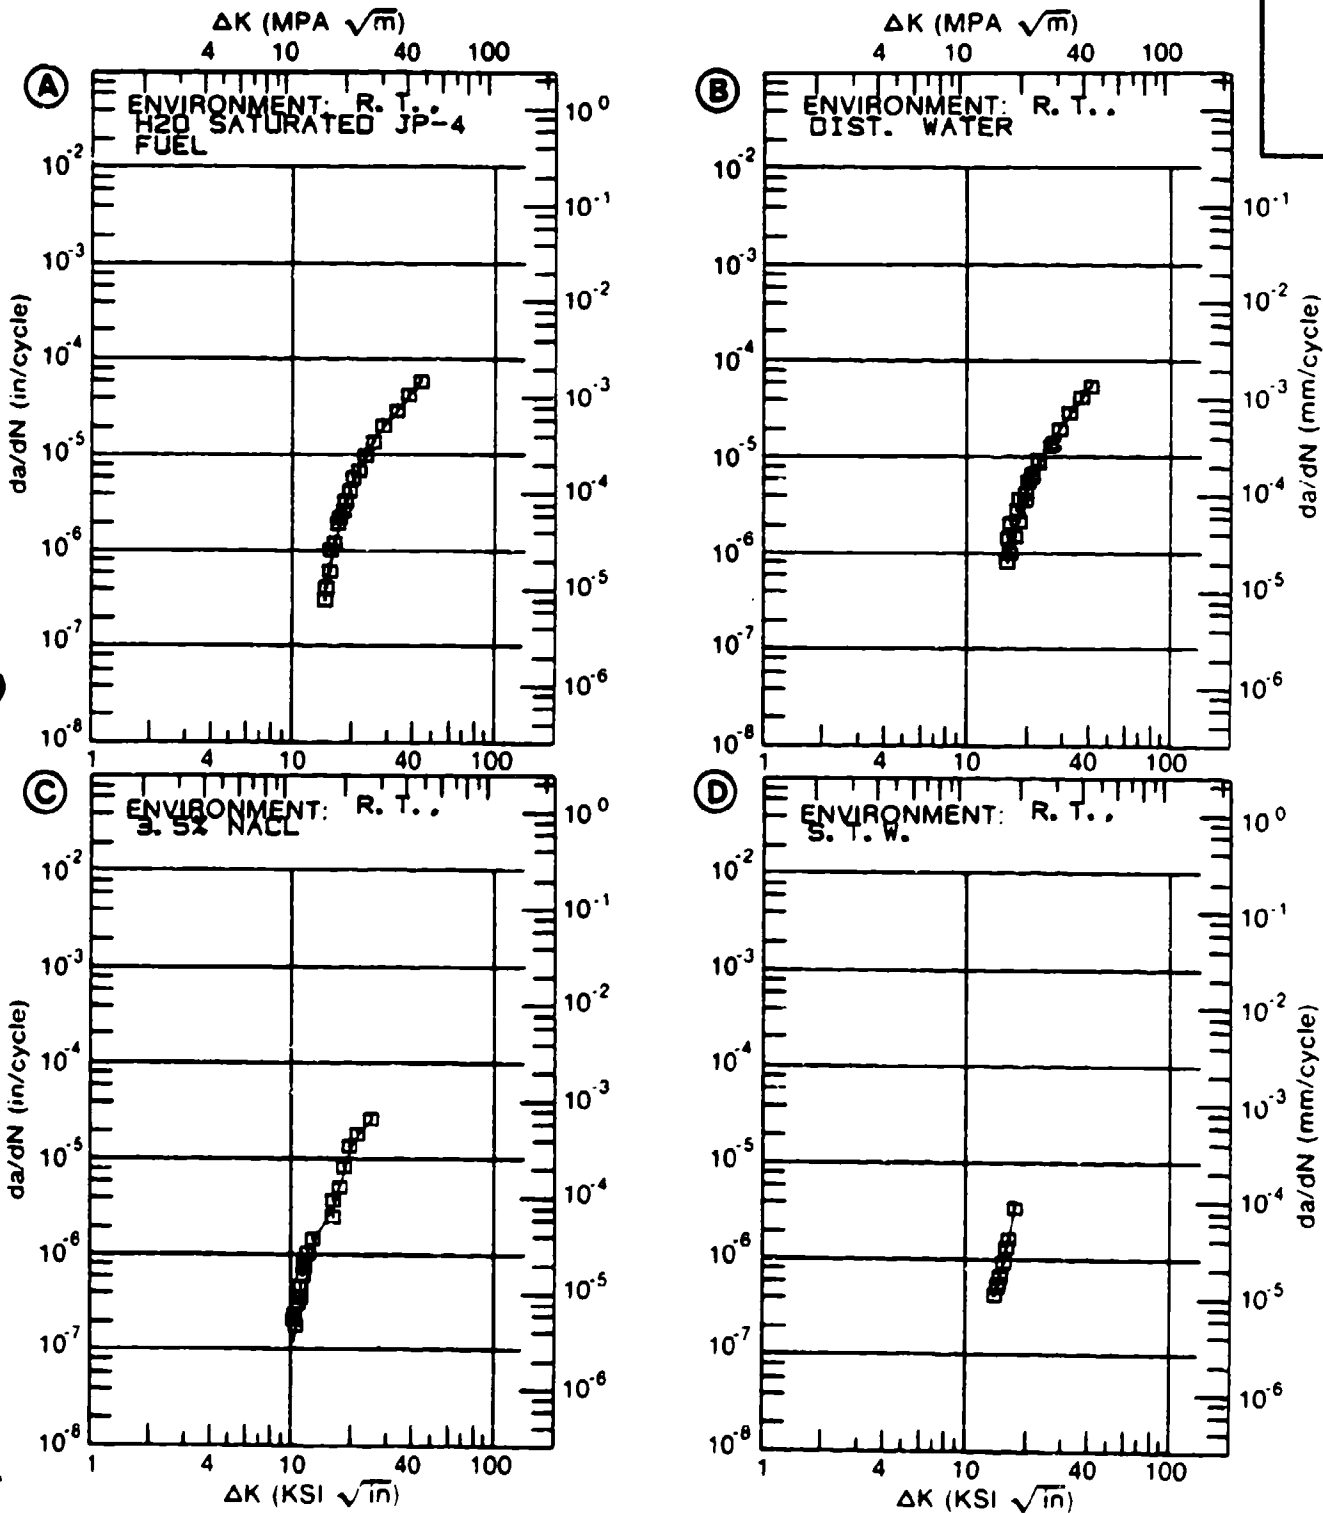


Figure 4.12.3.6

TABLE 4.12.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.7 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: BA

TI-6AL-4V (ELI)

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. H2O SATURATED JP-4 FUEL	E= R. T. ALT JP4-FUEL & DIST. WATER	E= R. T. DIST. WATER	
DELTA K	A: 27.33	19.4			
MIN	B: 26.24		19.2		
	C: 42.57			63.1	
	D:				
	30.00	26.4	31.1		
	35.00	40.8	48.9		
	40.00	57.7	69.0		
	50.00	106.	122.	141.	
	60.00	200.	212.	210.	
	70.00	402.	388.	383.	
DELTA K	A: 72.48	483.			
MAX	B: 73.62		489.		
	C: 74.51			607.	
	D:				
ROOT MEAN SQUARE		10.21	12.84	5.17	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 98140

TITAN.
 ALLOY

TI-6AL-
 4V (ELI)

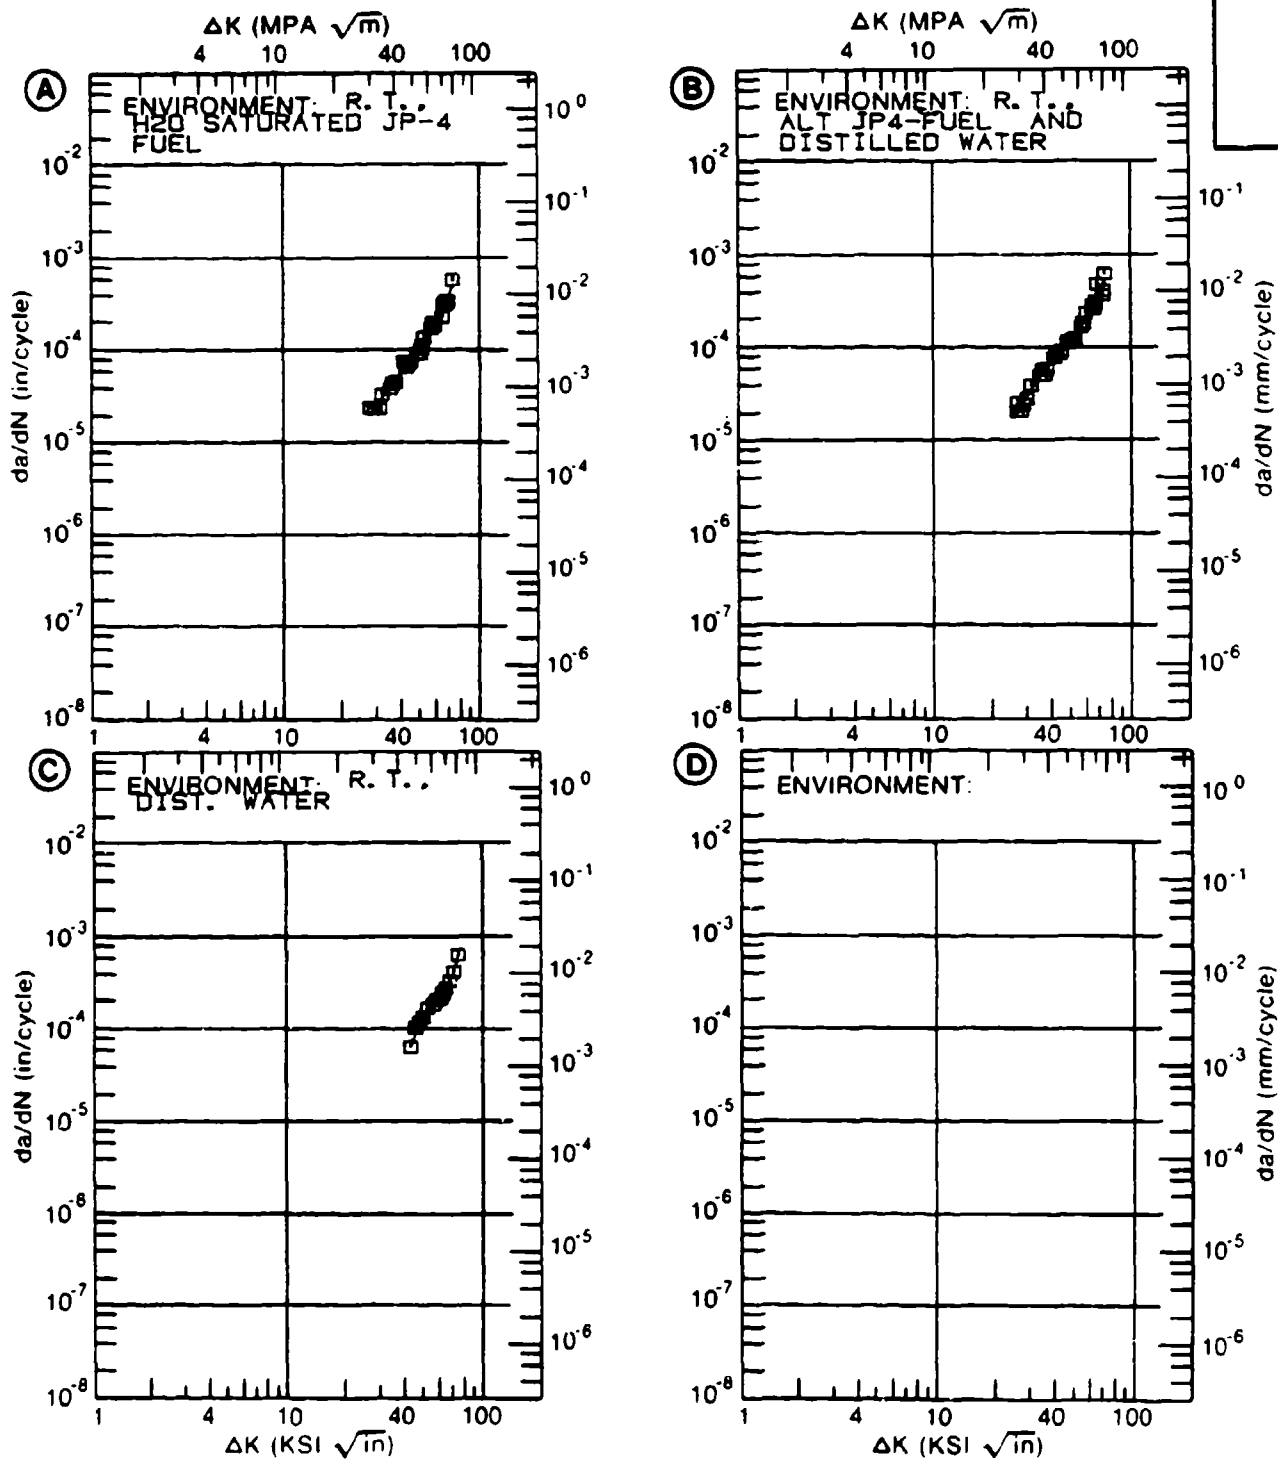


Figure 4.12.3.7

TABLE 4.12.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.8 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. 3. 5% NACL	E= R. T. S. T. W.		
DELTA K MIN	A: 26. 53 :	51. 6			
	B: 27. 01 :		37. 8		
	C:				
	D:				
	30. 00 :	74. 9	53. 2		
	35. 00 :	107.	70. 8		
DELTA K MAX	40. 00 :	138.	89. 9		
	50. 00 :	214.	214.		
	60. 00 :	355.	616.		
	70. 00 :	657.			
	A: 73. 43 :	833.			
	B: 64. 60 :		757.		
C:					
D:					
ROOT MEAN SQUARE		7. 81	10. 86		
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25				
SUMMARY	1. 25-2. 0				
(NP/NA)	>2. 0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 88140

TITAN.
 ALLOY

TI-6AL-4V (ELI)

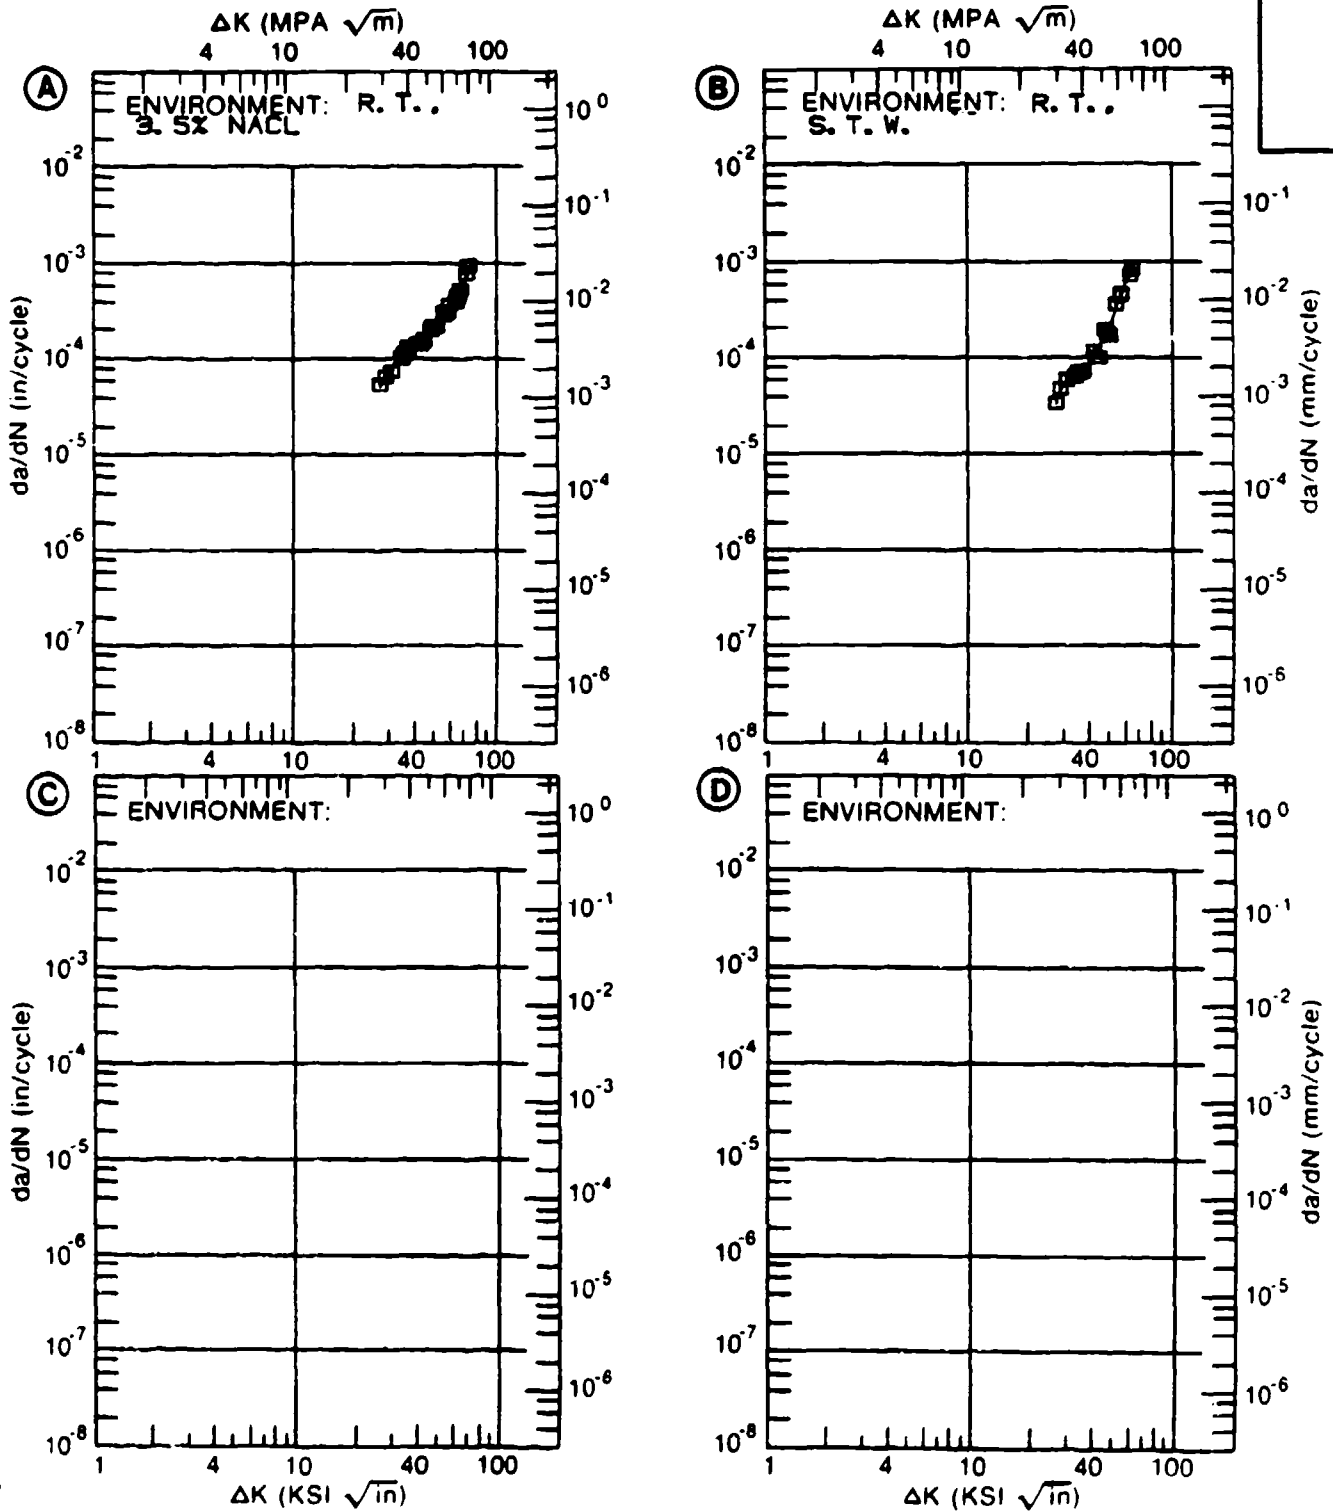


Figure 4.12.3.8

TABLE 4.12.3.9

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.9 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. H2O SATURATED JP-4 FUEL	E= R. T. 3.5% NAACL		
DELTA K MIN	A: 26.50	15.3			
	B: 26.84		11.0		
	C:				
	D:				
	30.00	28.0	36.5		
	35.00	47.5	110.		
	40.00	67.9	194.		
	50.00	123.	353.		
	60.00	230.	624.		
	70.00	501.	1449.		
DELTA K MAX	A: 76.78	1014.			
	B: 75.41		2636.		
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		10.69	18.13		
1.0-1.25	0.0-0.5				
0.5-1.0	0.5-0.8				
0.25-0.5	0.2-1.25				
0.1-0.25	1.0-2.0				
0.05-0.1	2.0-5.0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 0.10 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 88140

TITAN.
 ALLOY

TI-6AL-
 4V (ELI)

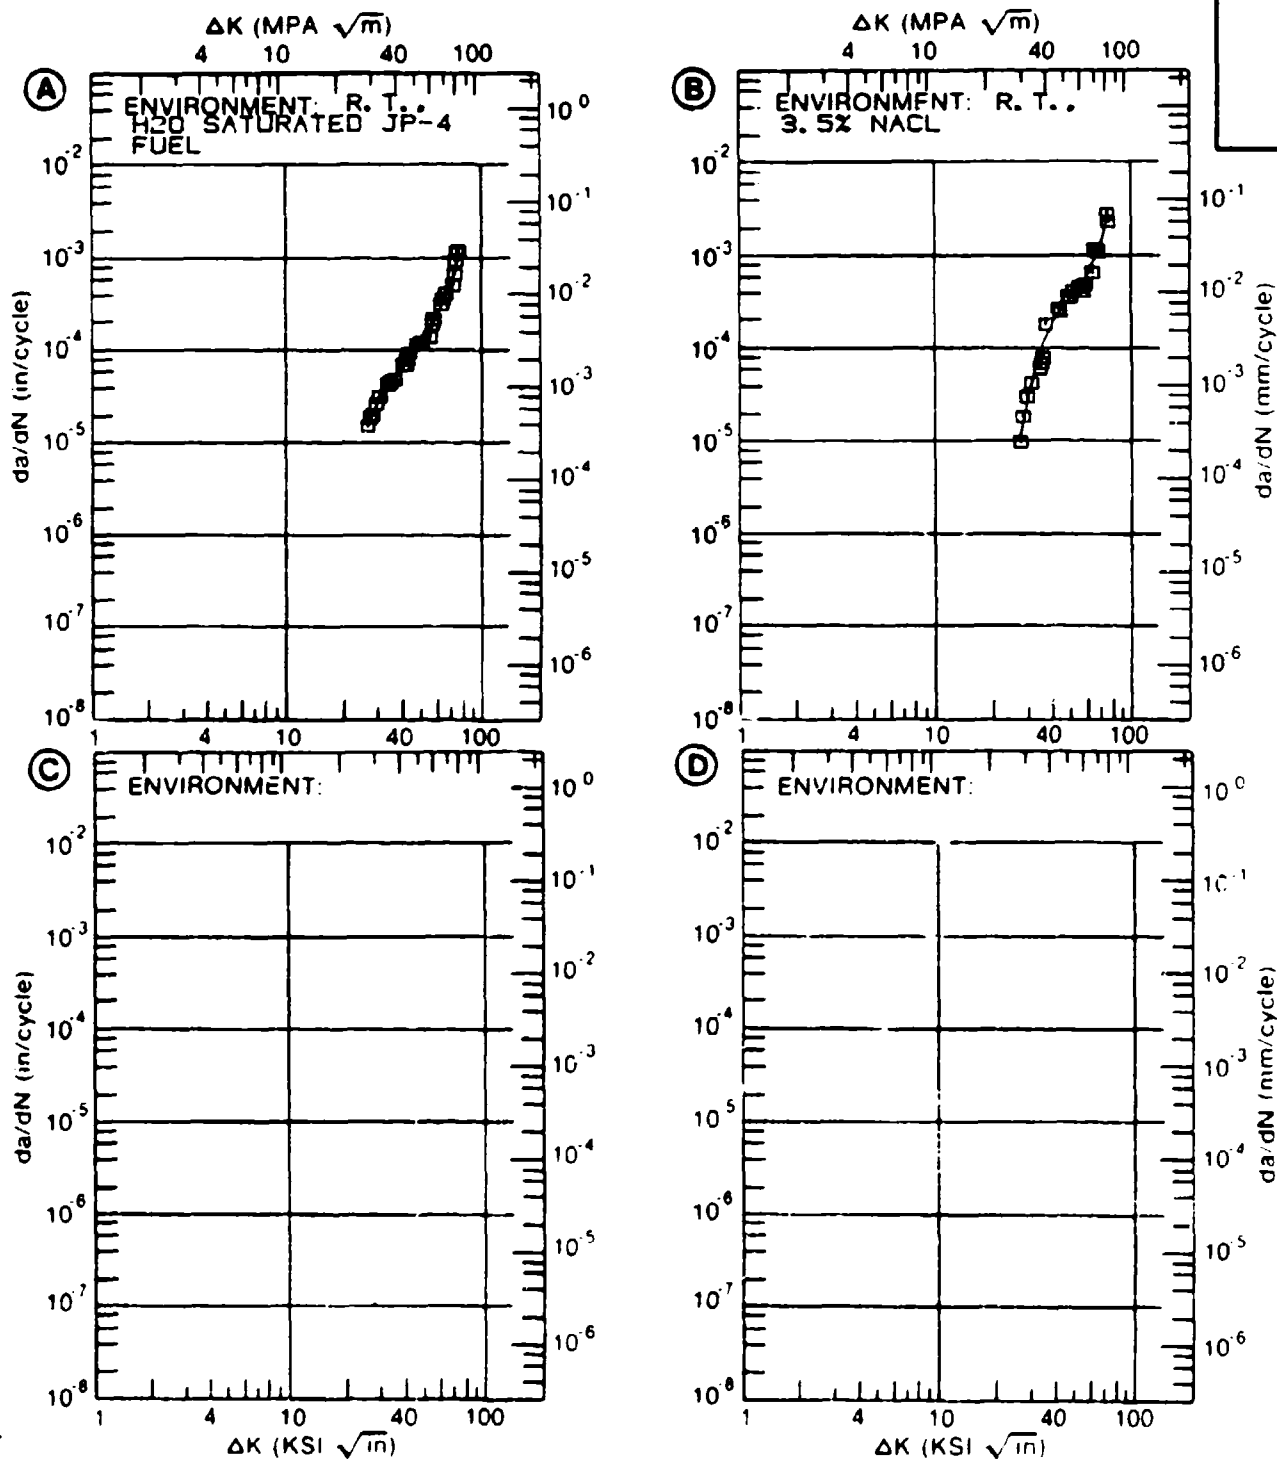


Figure 4.12.3.9

TABLE 4.12.3.10

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.10 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN./CYCLE)			
		A	B	C	D
		E-- 65F NITROGEN & AIR			
DELTA K	A: 15.30	2.20			
MIN	B:				
	C:				
	D:				
	16.00	2.69			
	20.00	9.07			
	25.00	15.4			
	30.00	22.0			
	35.00	33.1			
	40.00	53.4			
DELTA K	A: 42.13	66.9			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		11.19			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES 8B140

TITAN.
 ALLOY
 TI-6AL-
 4V (ELI)

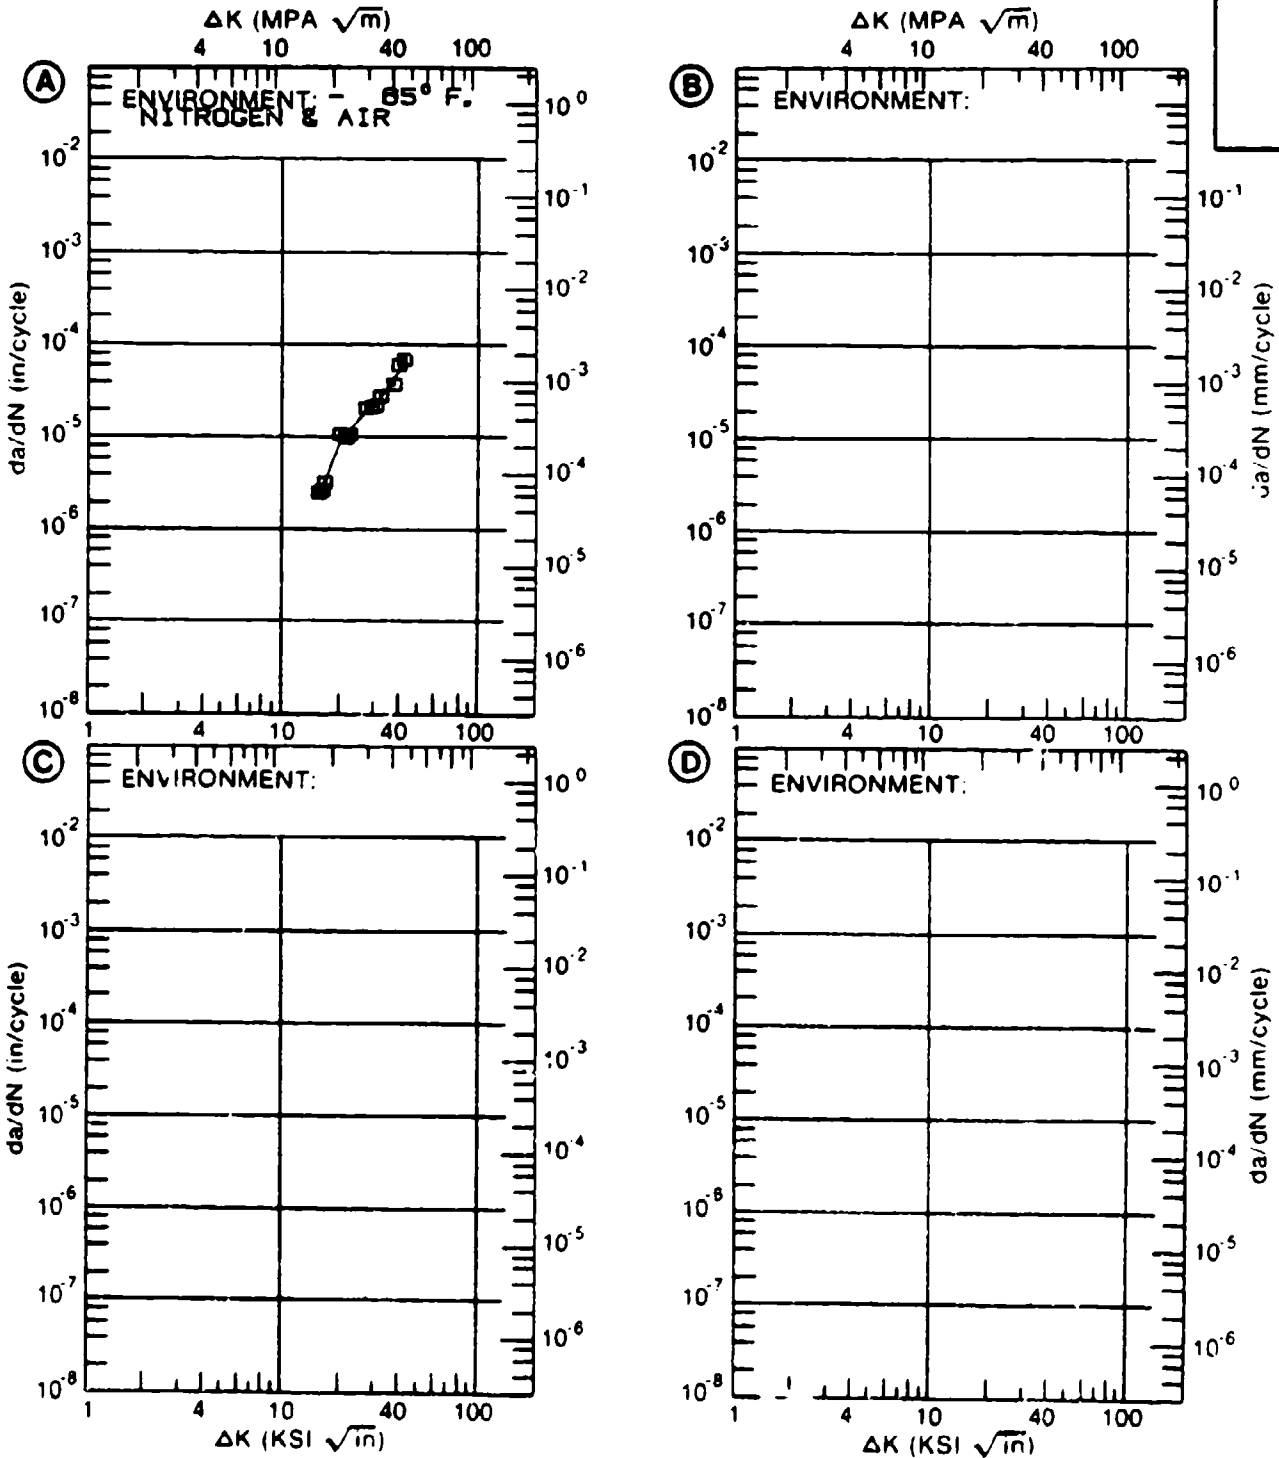


Figure 4.12.3.10

TABLE 4.12.3.11

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.11 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E=+ 175F DRY AIR	E=+ 175F JP-4 FUEL	E=+ 175F DIST. WATER	E=+ 175F 3.5% NaCl
DELTA K	A: 15.15	4.42			
MIN	B: 14.71		3.87		
	C: 21.49			19.1	
	D: 15.01				5.51
	16.00	5.69	5.02		6.93
	20.00	12.1	13.3		17.8
	25.00	20.7	24.0	29.8	48.6
	30.00	33.5	36.9	50.4	100.
	35.00	56.1	59.6	73.3	159.
	40.00	78.0	99.0	91.9	
DELTA K	A: 40.96	80.3			
MAX	B: 42.28		101.		
	C: 41.36			95.5	
	D: 35.56				165.
ROOT MEAN SQUARE		9.05	14.61	7.92	12.39
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 88140

TITAN.
 ALLOY

TI-6AL-4V (ELI)

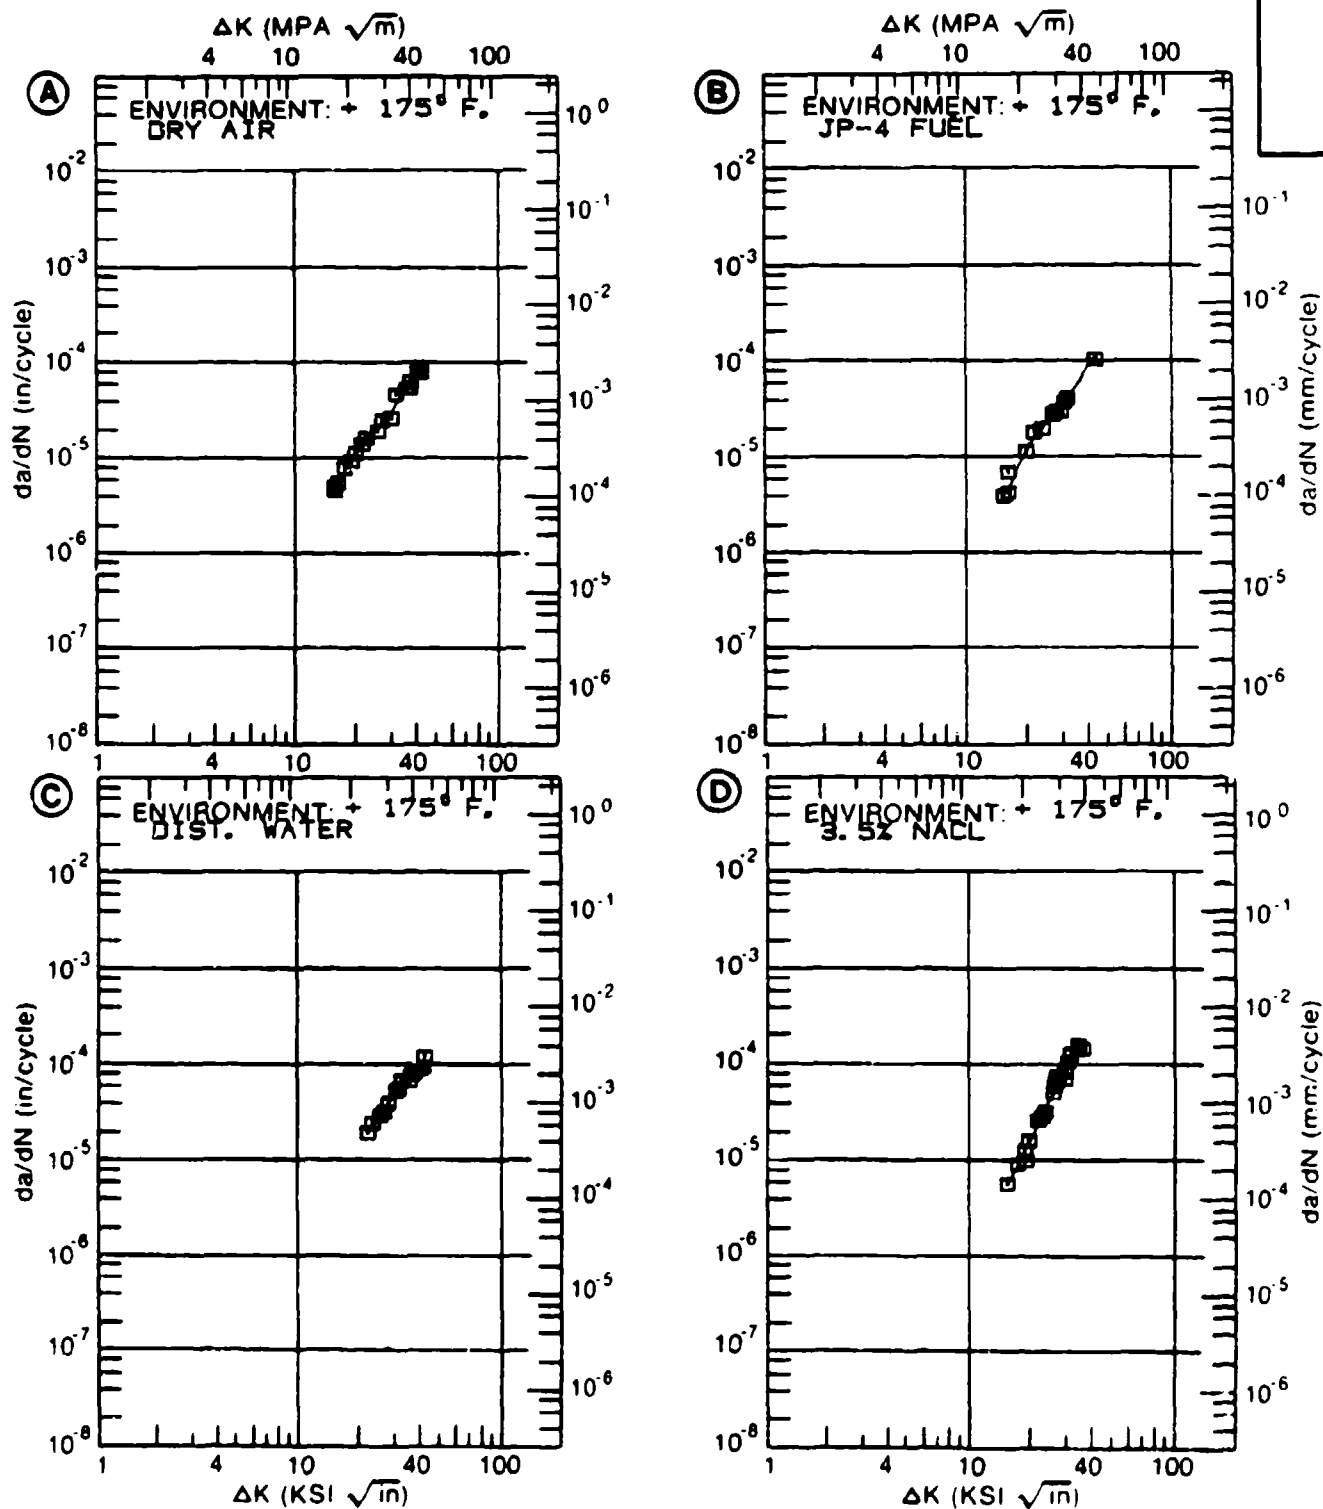


Figure 4.12.3.11

TABLE 4.12.3.12

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.12 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. H2O SATURATED JP-4 FUEL	E= R. T. ALT JP4-FUEL & DIST. WATER	E= R. T. DIST. WATER	
DELTA K MIN	A: 10.91	.61			
	B: 10.34		.50		
	C: 9.85			.23	
	D:				
	10.00			.273	
	13.00	2.24	2.19	2.03	
	16.00	6.47	5.87	6.01	
	20.00	13.8	12.9	13.7	
	25.00	24.6	23.5	25.5	
	30.00	39.7	35.5	40.7	
	35.00	66.0	50.1	63.0	
	40.00	117.		98.7	
DELTA K MAX	A: 41.26	137.			
	B: 36.59		55.4		
	C: 44.21			148.	
	D:				
ROOT MEAN SQUARE		22.06	20.98	16.08	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 99140

TITAN.
 ALLOY

TI-6AL-
 4V (ELI)

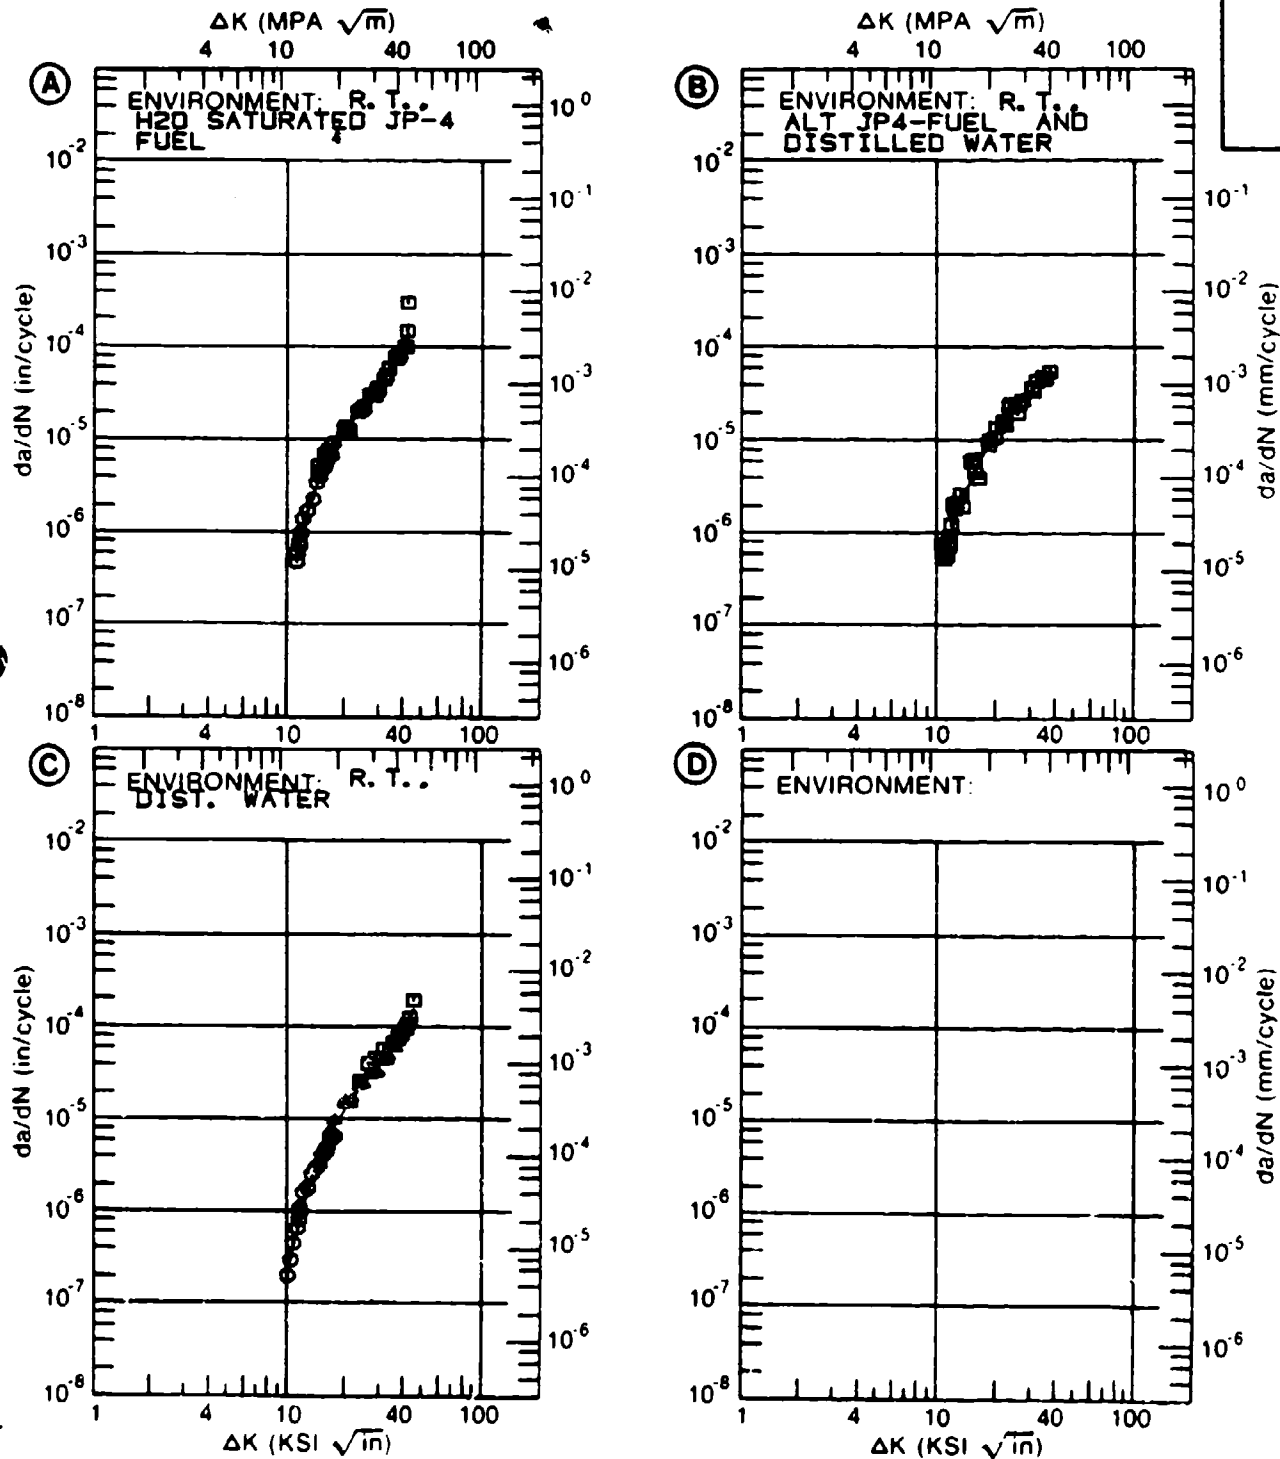


Figure 4.12.3.12

TABLE 4.12.3.13

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.12.3.13 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. 3.5% NaCl	E= R. T. S. T. W.		
DELTA K A:	10.16	.980			
DELTA K B:	9.76		.991		
MIN C:					
D:					
	10.00		1.13		
	13.00	2.61	3.77		
	16.00	7.36	9.26		
	20.00	31.3	28.2		
	25.00	69.0	62.3		
	30.00	115.	86.9		
	35.00	184.	120.		
	40.00	308.	196.		
DELTA K A:	40.69	333.			
DELTA K B:	42.18		258.		
MAX C:					
D:					
ROOT MEAN SQUARE		18.54	15.96		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 00140

TITAN.
 ALLOY

TI-6AL-
 4V (ELI)

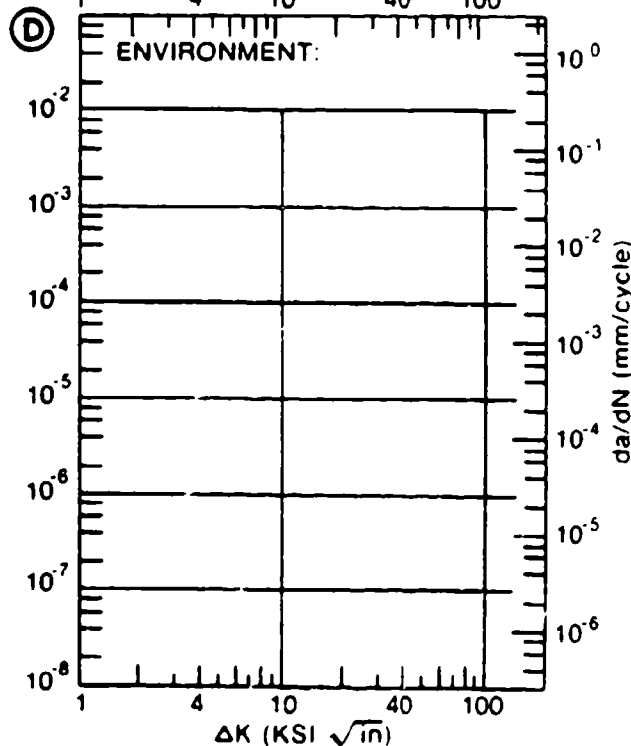
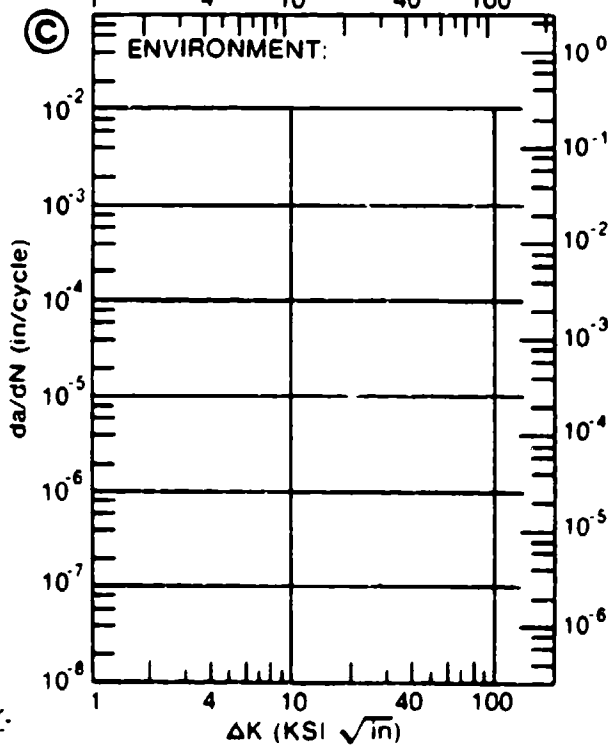
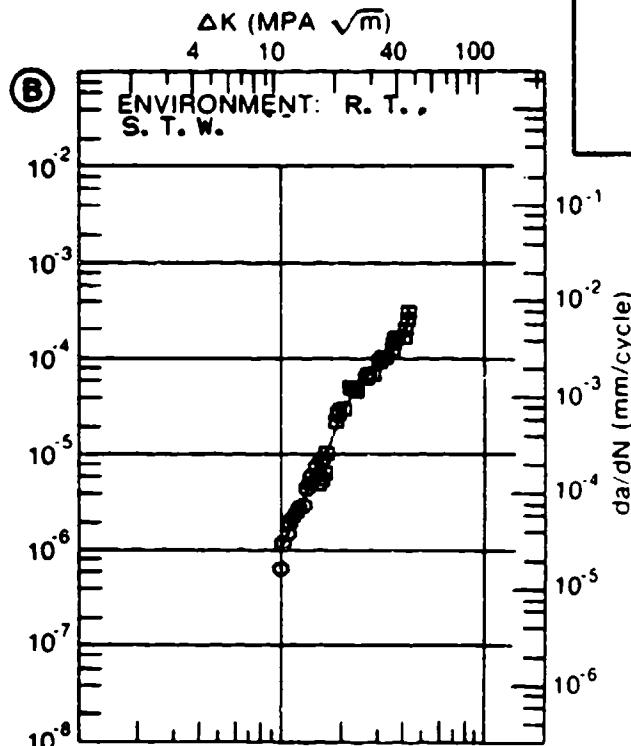
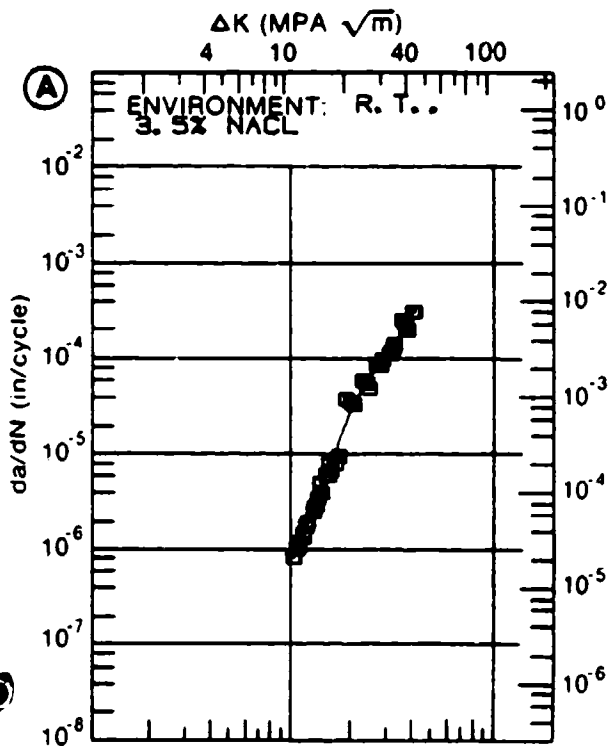


Figure 4.12.3.13

TABLE 4.12.3.14

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.14 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. : DRY AIR			
DELTA K MIN	A: 10.10	.424			
	B:				
	C:				
	D:				
	13.00	2.46			
	16.00	6.34			
	20.00	12.8			
25.00	22.4				
30.00	36.2				
35.00	60.4				
40.00	107.				
DELTA K MAX	A: 40.48	113.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		20.59			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 0.10- 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES 00140

TITAN.
 ALLOY

TI-6AL-
 4V (ELI)

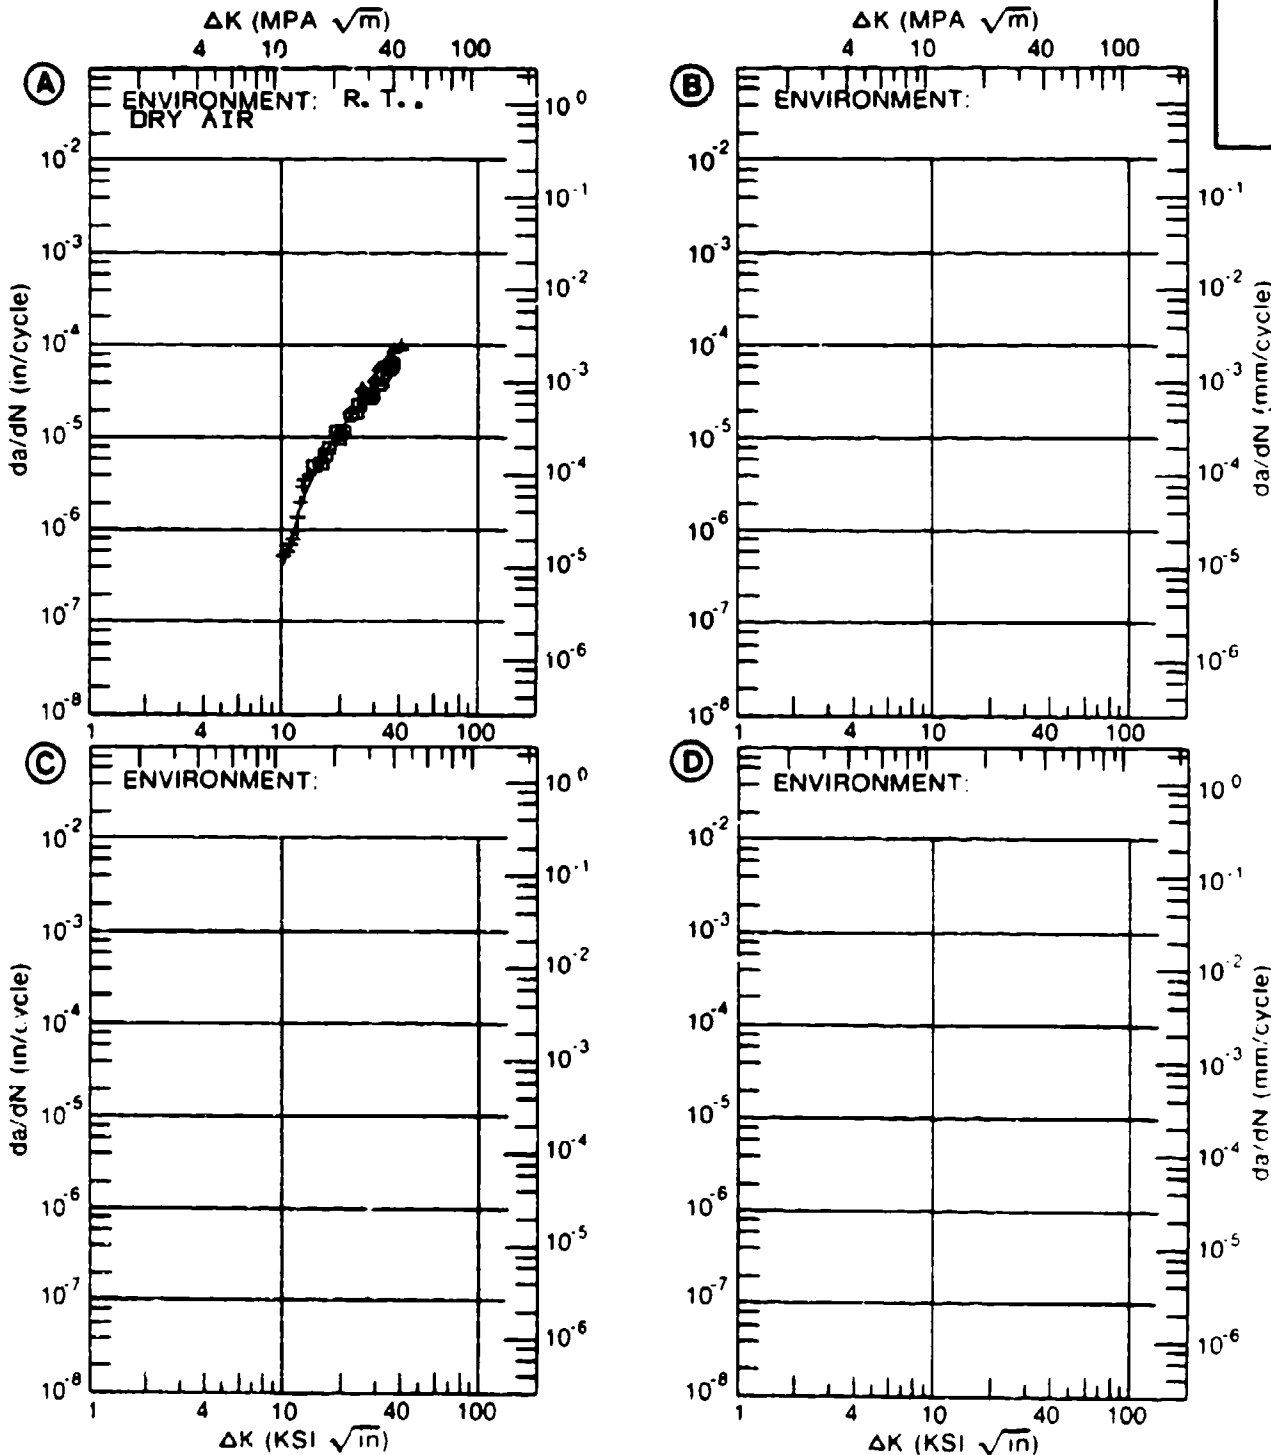


Figure 4.12.3.14

TABLE 4.12.3.15

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.15 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: BA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. H2O SATURATED JP-4 FUEL	E= R. T. 3. 5% NACL	E= R. T. S. T. W.	
DELTA K	A: 14.08	3.65			
MIN	B: 15.54		5.62		
	C: 15.38			4.56	
	D:				
	16.00	6.63	6.80	5.42	
	20.00	13.9	15.0	12.7	
	25.00	25.0	37.8	27.2	
	30.00	42.8	178.	54.1	
	35.00	78.6	264.	110.	
	40.00			233.	
DELTA K	A: 37.10	105.			
MAX	B: 35.28		264.		
	C: 42.70			357.	
	D:				
ROOT MEAN SQUARE		7.84	21.27	9.49	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/MA)	>2.0				

CONDITION/HT: BA
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 STRESS RATIO: +0.50
 FREQUENCY: 0.10 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 00140

TITAN.
 ALLOY
 TI-6AL-
 4V (ELI)

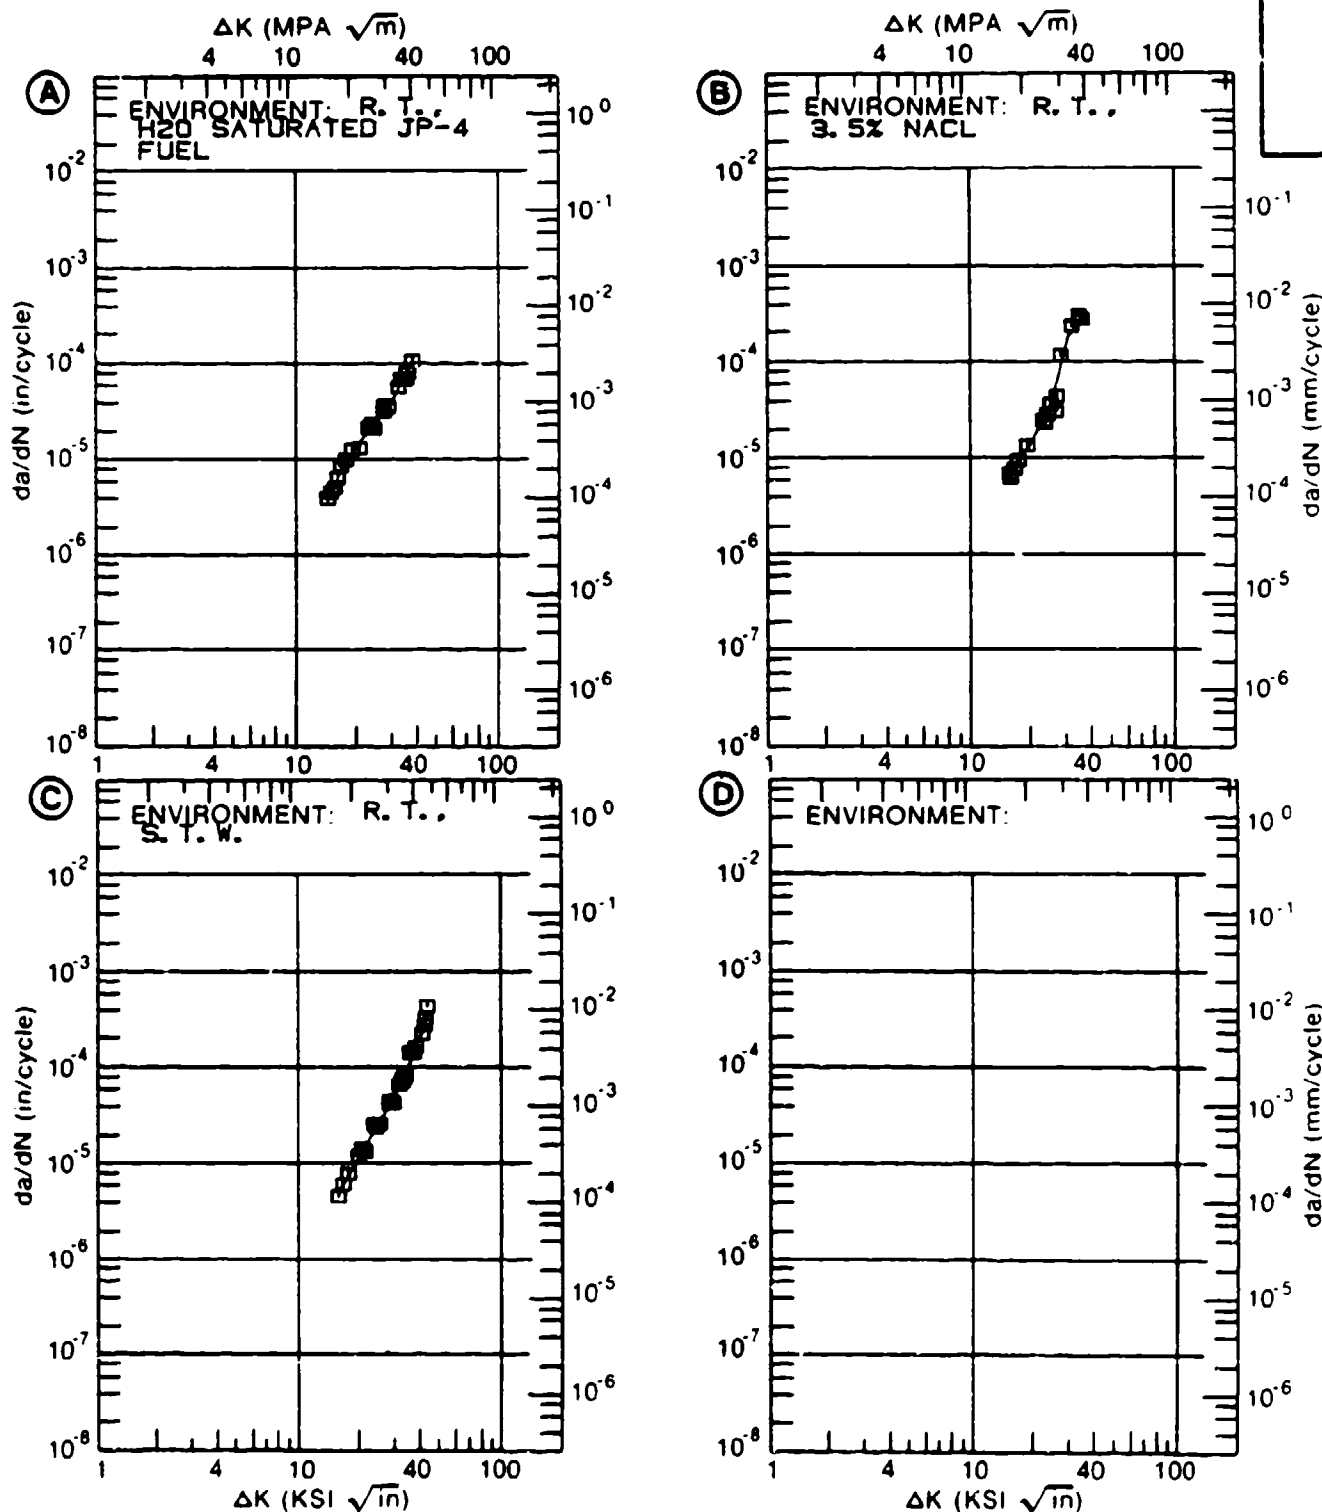


Figure 4.12.3.15

TABLE 4.12.3.16

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.16 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: RA

TI-6AL-4V (ELI)

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	E= R. T. LAB AIR 10HZ		E= R. T. SIM. SEA WATER 1-10HZ	
DELTA K MIN	A: 12.94	.519	B: 10.88	3.44
	13.00	.565		3.90
	16.00	4.94		7.39
	20.00	10.8		15.0
	25.00	19.4		32.1
	30.00	30.8		64.3
	35.00	50.6		121.
	40.00	91.5		204.
	50.00			393.
DELTA K MAX	A: 47.16	202.	B: 50.76	404.

ROOT MEAN SQUARE PERCENT ERROR 33.80 20.45

LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5		
	0.5-0.8	1	
	0.8-1.25		2
	1.25-2.0	1	
	>2.0		

CONDITION/HT: RA
 FORM: 3.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY:

YIELD STRENGTH: 119.4 KSI
 ULT. STRENGTH: 127.8 KSI
 SPECIMEN THK: 1.003- 1.040"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: NC002

TITAN.
 ALLOY

TI-6AL-4V (ELI)

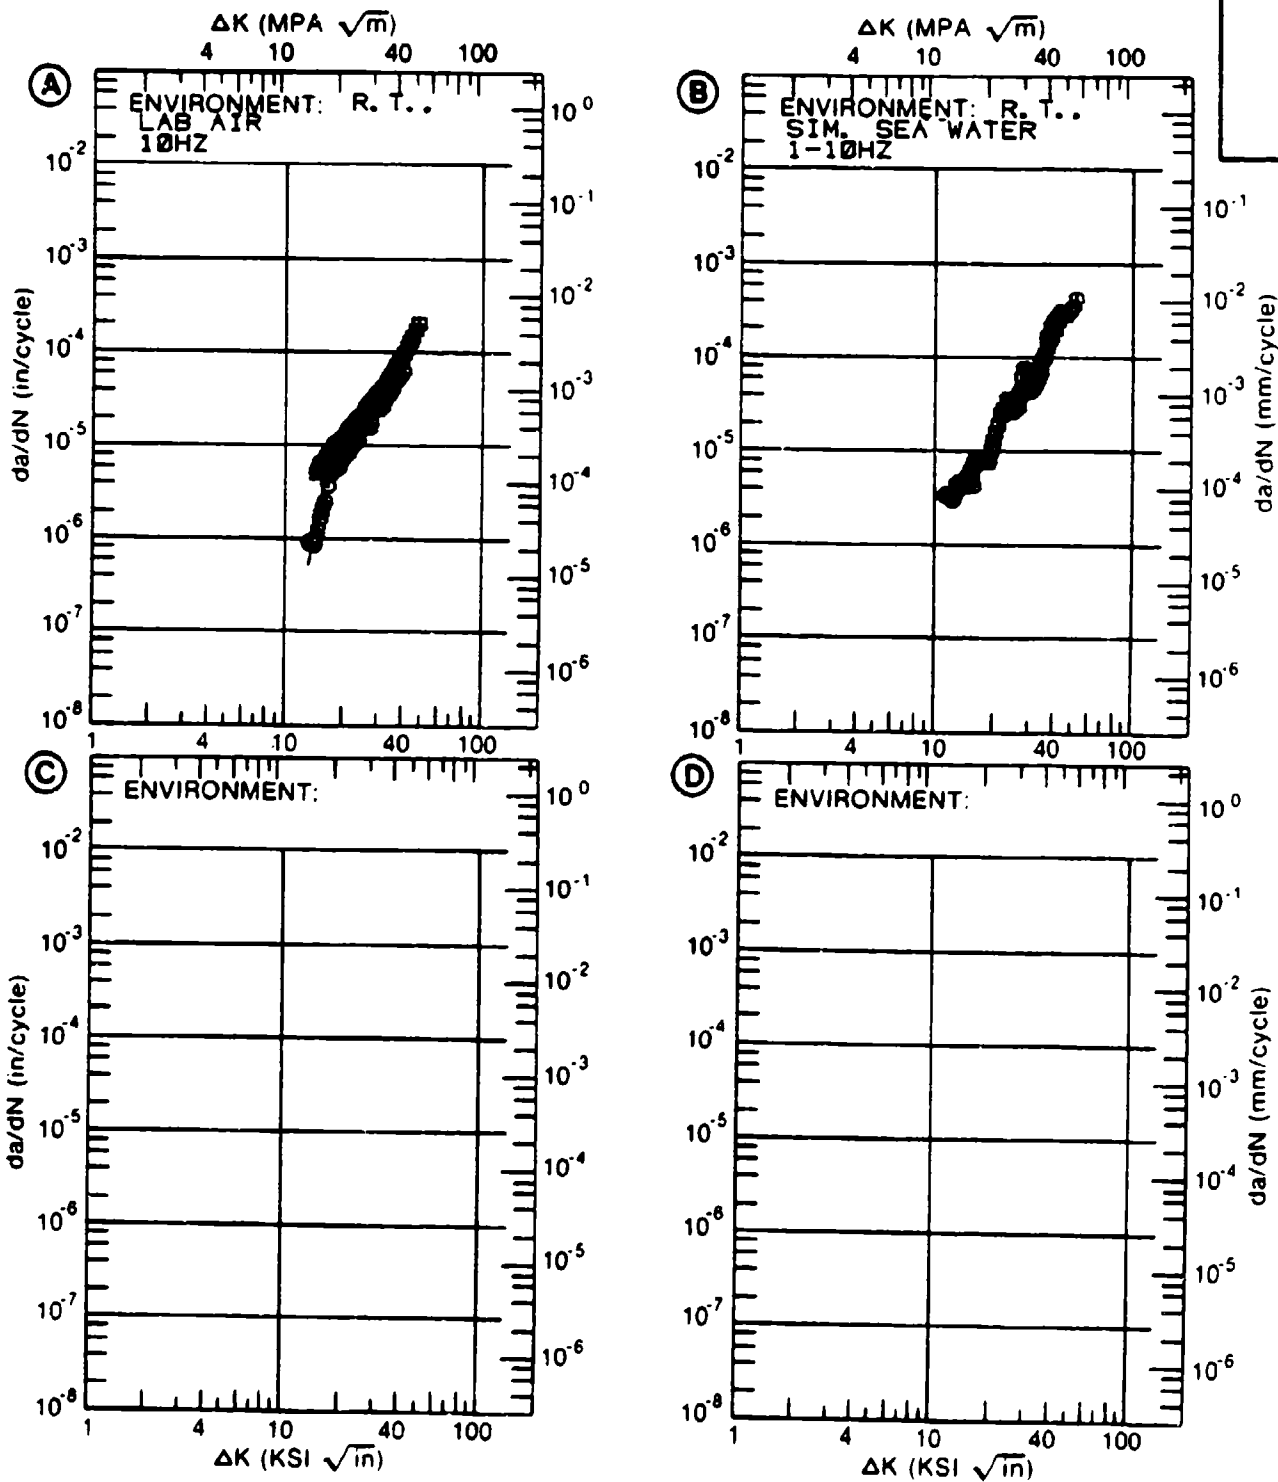


Figure 4.12.3.16

TABLE 4.12.3.17

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.12.3.17 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-4V (ELI)			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E= R. T. SIM. SEA WATER		
DELTA K MIN	A: 12.57	1.50			
	B: 13.17		2.76		
	C:				
	D:				
	13.00	1.71			
	16.00	3.68	3.88		
	20.00	7.75	7.96		
	25.00	16.0	20.1		
	30.00	29.4	45.1		
	35.00	51.4	87.4		
	40.00	87.2	146.		
	50.00	240.			
	60.00	638.			
DELTA K MAX	A: 67.29	1287.			
	B: 45.43		221.		
	C:				
	D:				
ROOT MEAN SQUARE		16.76	30.38		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0		1 2 1		1 1

CONDITION/HT: RA
 FORM: 3.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 1.00- 10.00 HZ

YIELD STRENGTH: 122.0 KSI
 ULT. STRENGTH: 130.2 KSI
 SPECIMEN THK: 0.923- 1.010"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: NC002

TITAN.
 ALLOY

TI-6AL-
 4V (ELI)

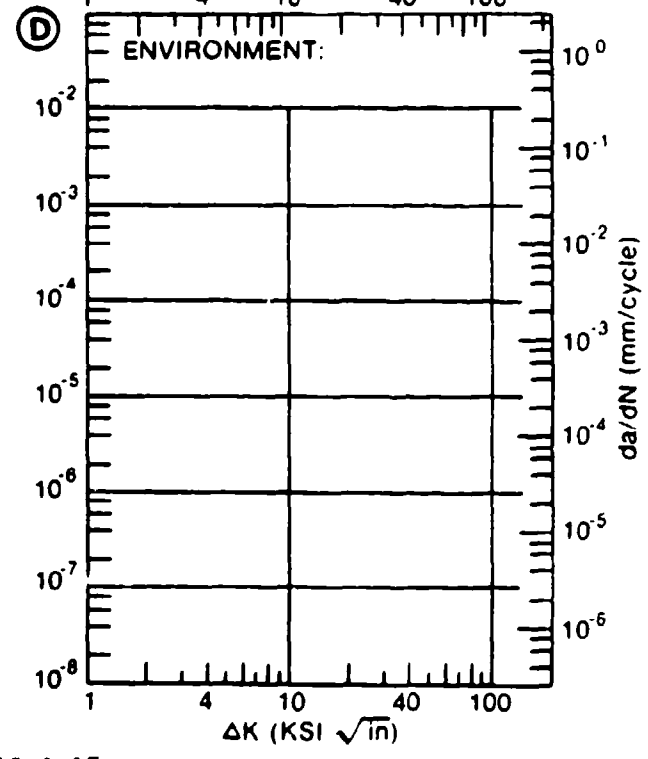
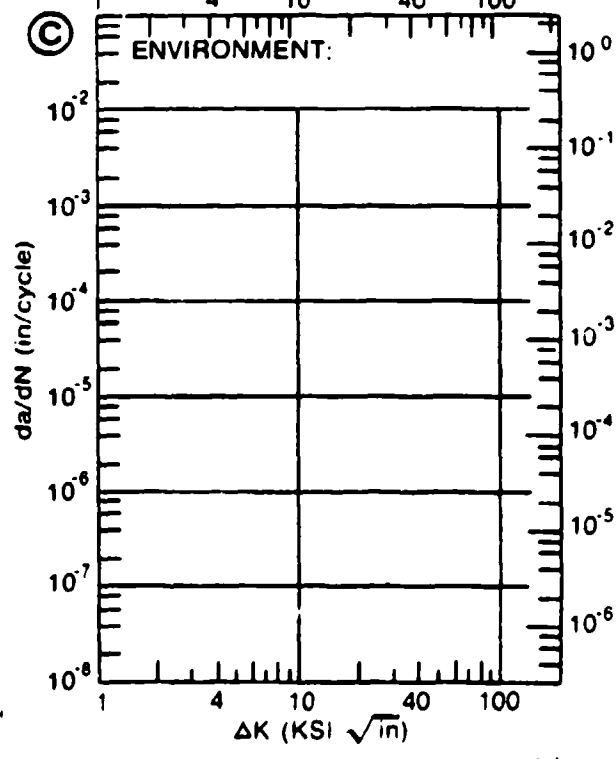
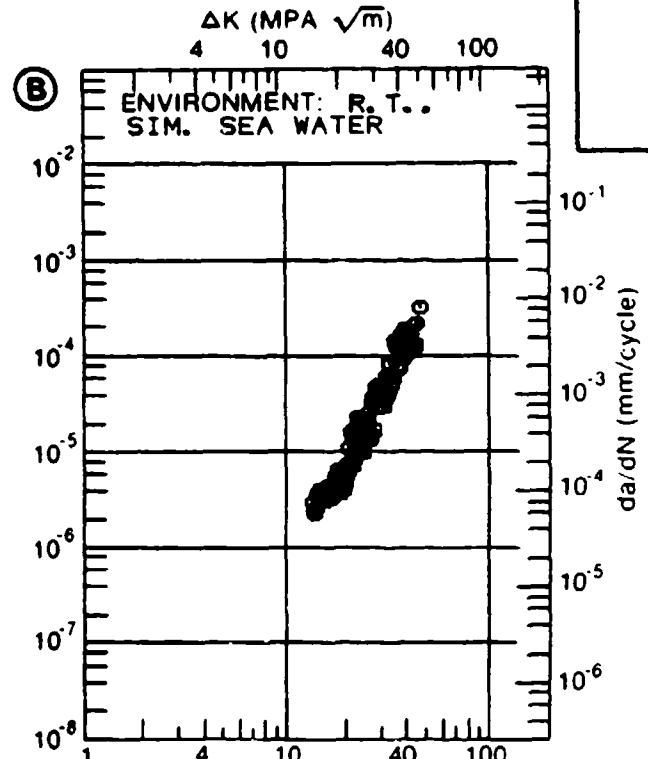
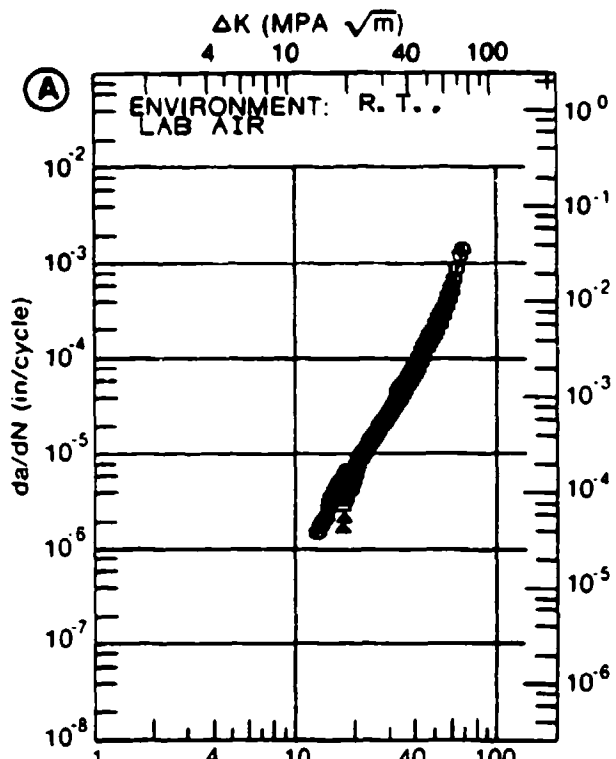


Figure 4.12.3.17

TABLE 4.12.3.18

CONDITION	--PRODUCT--		TEST TEMP OR (F)	SPEC YIELD STR (KSI)	ENVIRONMENT	TITANIUM		TI-6AL-4V(ELI) K(1SCC)		WIDTH (IN)	THICK (IN)	DESIGN (IN)	CRACK LENGTH (IN)	K(0) K(1SCC) MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
	FORM	THICK (IN)				W	B	A									
100%F 1HR HELIUM COOL	F	1.00	R.T	115.2	3.5 PCT NACL	1.000	0.500	CANT*	112.00	84.00*							1967 70931

*NOTE--DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(K1SCC/TYB)SQUARED

TABLE 4.13.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
TITANIUM ALLOY TI-6AL-6V-2SN AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN))	DEVIATION (NUMBER OF SPECIMENS)
	CLATE	
	L-I	B-I
BETA ANNEAL 1810F 1 HR. ARGON COOL	---	54.3 ± 2.0 (7)
BETA ANNEAL & BTDA-1800F 0.5HR.AC. 1975F 0.5HR.WG. 1050F 8 HR.AC	50.1 ± 1.8 (2)	---
DUPLEX ANNEAL	---	65.1 ± 2.0 (3)
MILL ANNEALED	---	39.0 ± 3.2 (4)
BTA-1675F 0.25 HR.WG. 100F 4 HR	---	34.1 ± 3.8 (3)
BTDA-1700F 1 HR.WG. 1400F 1 HR.AC	42.9 ± 1.2 (3)	46.1 ± 3.1 (4)
	FORGING	
	L-I	B-I
MILL ANNEALED	38.6 ± 2.7 (3)	---
BTA-1600F 0.5HR.WG. 1000F 6 HR.AC	30.8 ± 0.7 (3)	---

TABLE 4.13.1.1 (Con't)

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
TITANIUM ALLOY TI-6AL-6V-2SN AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION		(NUMBER OF SPECIMENS)	
	L-I	I-L	L-I	I-L
MILL ANNEALED	32.3 ± 6.4 (4)	---	---	8-L
MILL ANNEALED 1000F 2 HR. AC	57.1 ± 2.2 (2)	---	---	---
STDA-1700F 1 HR. WQ. 1400F 1 HR. AC	62.8 ± 6.9 (4)	57.0 ± 3.7 (4)	---	---

TABLE 4.13.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-6V-2SN

TEST CONDITIONS

SPECIMEN ORIENTATION L-S

ENVIRONMENT H H A
AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 5 10 20 50 100	
ST0A	PLATE	0 10	0 10		1 73 10 2
ST0A	PLATE	0 10	10 00		2 58 9 03

TABLE 4.13.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-6V-2SN

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT H M A
A T R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
ST0A	PLATE	0.10	1.00				1.64	15.1	396		
ST0A	PLATE	0.10	20.00			0.11	1.76	13.4			

TABLE 4.13.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-6V-2SN

TEST CONDITIONS

SPECIMEN
ORIENTATION L-TENVIRONMENT 3.5% NaCl
AT R. T.

CONDITION/MT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2.5	5	10	20	50	100
STDA	PLATE	0.10	1.00			2.35	38.4	2560		
STDA	PLATE	0.10	20.00			0.23	3.13	19.3		

TABLE 4.13.1.5

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-6V-2SN

TEST CONDITIONS

SPECIMEN
ORIENTATION T-S

ENVIRONMENT

M.H.A.
A.R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	2.5	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
STDA	PLATE	0.10	0.10				1.15	41.6			
STDA	PLATE	0.50	0.10				2.67	63.9			

TABLE 4.13.1.6

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-6V-2SN

TEST CONDITIONS

SPECIMEN ORIENTATION T-S

ENVIRONMENT 3.5% NaCl AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5	5
				10	20
				50	100
BA	PLATE	0.10	0.10-10.00		1.31
ST0A	PLATE	0.10	1.00		1.49 92.1

TABLE 4.13.1.7

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

TITANIUM TI-6AL-6V-2SN

IFSI CONDITIONS		ENVIRONMENT	FREQ (HZ)	STRESS RATIO	PRODUCT FORM	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
SPECIMEN ORIENTATION	T-L						2.5	5	10	20	50	100
ST0A		HUMID AIR AT R.T	10.00	0.10	PLATE			2.16	12.4			
ST0A			10.00	0.10	PLATE			0.73	5.98	42.3		
ST0A			10.00	0.50	PLATE		0.33	2.38	49.5			

TABLE 4.13.2.1

TITANIUM		TI-6AL-6V-2SN		K(IIC)		K(IIC)		K(IIC)		K(IIC)		K(IIC)		K(IIC)		K(IIC)	
CONDITION	FORM	THICK (IN)	TEMP (F)	ORIENT	YIELD (KSI)	WIDTH (IN)	THICK (IN)	DESIGN (IN)	CRACK LENGTH (IN)	2.5* (IN)	M(IIC)/YB**2 (KSI*GRY IN)	M(IIC) MEAN (IN)	STAN DEV	DATE	REFER	K(IIC)	
																A	B
ANNEAL-COARSE GRAIN-1350F 2 HR.AC	F	1 00	R.T.	--	143 0	2 000	1 000	CT	1 000	0 70	75 60	75 60		1974	88962		
		1 00			143 0	2 000	1 000	CT	1 000	0 52	63 00	63 00		1974	88962		
		1 00			143 0	2 000	1 000	CT	1 000	0 48	62 80	62 80		1974	88962		
		1 00			143 0	2 000	1 000	CT	1 000	0 52	63 00	63 00		1974	88962		
		1 00			143 0	2 000	1 000	CT	1 000	0 65	73 20	73 20		1974	88962		
		1 00			143 0	2 000	1 000	CT	1 000	0 76	78 80	70 1/	6 6	1974	88962		
ANNEAL-FINE GRAIN-1350F 2 HR.AC	F	6 00	R.T.	--	148 0	2 000	1 000	CT	1 000	0 34	54 40	54 40		1974	88962		
		6 00			148 0	2 000	1 000	CT	1 000	0 36	56 60	56 60		1974	88962		
		6 00			148 0	2 000	1 000	CT	1 000	0 32	53 80	53 80		1974	88962		
		6 00			148 0	2 000	1 000	CT	1 000	0 34	54 60	54 60		1974	88962		
		6 00			148 0	2 000	1 000	CT	1 000	0 29	50 30	50 30		1974	88962		
		6 00			148 0	2 000	1 000	CT	1 000	0 34	54 40	54 0/	2 1	1974	88962		
ANNEALED 10-20 10-20% PRIMARY ALPHA ANNEALED 1350F 2 HR.AC	F	2 50	R.T.	--	145 0	2 000	1 000	CT	1 000	0 30	50 40	50 40		1974	88962		
		2 50			145 0	2 000	1 000	CT	1 000	0 31	51 30	50 9/	0 6	1974	88962		
ANNEALED 40-50 40-50% PRIMARY ALPHA ANNEALED 1350F 2 HR.AC	F	2 50	R.T.	--	149 0	2 000	1 000	CT	1 000	0 26	48 10	48 10		1974	88962		
		2 50			149 0	2 000	1 000	CT	1 000	0 28	49 40	49 40		1974	88962		
88-AB FIN-10 BETA BLOCKED, ALPHA-BETA FINISHED, 10% REDUCTION, SOLUTION TREATED & OVERAGED, 1650F 1 HR, W3, 1300F 2 HR.AC	F	2 50	R.T.	--	148 0	2 000	1 000	CT	1 000	0 54	68 70	68 70		1974	88962		
		2 50			148 0	2 000	1 000	CT	1 000	0 67	76 60	76 60		1974	88962		
		2 50			147 0	2 000	1 000	CT	1 000	0 83	84 70	84 70		1974	88962		
		2 50			147 0	2 000	1 000	CT	1 000	0 60	71 80	71 80		1974	88962		

TABLE 4.13.2.1 (Con't)

CONDITION	TITANIUM		TI-6AL-6V-2SN		K(1C)		YIELD STRENGTH (KSI)	WIDTH (IN)	THICKNESS (IN)	DESIGN	CRACK LENGTH (IN)	2.9% K(1C)/TVB**2 (IN)	K(1C) MEAN (MSE) (IN)	K(1C) STAN DEV (IN)	DATE	REFER
	FORM	THICKNESS (IN)	ORIENT	REDUCTION	MILL ANNEALED	1350F										
RB, AB FIN-10HA BETA BLOCKED, ALPHA-BETA FINISHED	F	2.50	R.T.	147.0	2.000	1.000	CT	1.000	0.64	74.60	77.0/	6.8			1974 88962	
RB, AB FIN-30 BETA BLOCKED, ALPHA-BETA FINISHED, 30% REDUCTION, SOLUTION TREATED & OVERAGED, 1650F 1 HR, NO. 1350F 2 HR.AC	F	2.50	R.T.	148.0	2.000	1.000	CT	1.000	0.47	64.30					1974 88962	
RB, AB FIN-30HA BETA BLOCKED, ALPHA-BETA FINISHED, 30% REDUCTION, MILL ANNEALED 1350F 2 HR.AC	F	2.50	R.T.	143.0	2.000	1.000	CT	1.000	0.49	64.40					1974 88962	
RB, AB FIN-30HA BETA BLOCKED, ALPHA-BETA FINISHED, 30% REDUCTION, SOLUTION TREATED & OVERAGED, 1650F 1 HR, NO. 1350F 2 HR.AC	F	2.50	R.T.	143.0	2.000	1.000	CT	1.000	0.51	65.40					1974 88962	
RB, B FIN-10 BETA BLOCKED, ALPHA-BETA FINISHED, 10% REDUCTION, SOLUTION TREATED & OVERAGED, 1650F 1 HR, NO. 1350F 2 HR.AC	F	2.50	R.T.	140.0	2.000	1.000	CT	1.000	0.69	73.60					1974 88962	
RB, B FIN-10HA BETA BLOCKED, ALPHA-BETA FINISHED, 10% REDUCTION, MILL ANNEALED 1350F 2 HR.AC	F	2.50	R.T.	140.0	2.000	1.000	CT	1.000	0.64	70.70					1974 88962	
RB, B FIN-10HA BETA BLOCKED, ALPHA-BETA FINISHED, 10% REDUCTION, MILL ANNEALED 1350F 2 HR.AC	F	2.50	R.T.	136.0	2.000	1.000	CT	1.000	0.66	71.70					1974 88962	
RB, B FIN-10HA BETA BLOCKED, ALPHA-BETA FINISHED, 10% REDUCTION, MILL ANNEALED 1350F 2 HR.AC	F	2.50	R.T.	136.0	2.000	1.000	CT	1.000	0.66	70.20					1974 88962	
BETA ANNEAL	P	1.00	R.T.	138.4	2.500	1.000	WDL		0.73	74.60					1977 JEM01	
BETA ANNEAL 1810F 1 HR. ARCON COOL	P	0.50	R.T.	139.8	1.000	0.447	CT	0.348	0.36	53.20					1971 83222	
		0.50		139.8	1.000	0.447	CT	0.313	0.41	56.60					1971 83222	
		0.50		139.8	1.000	0.446	CT	0.558	0.36	53.00					1971 83222	

TABLE 4.13.2.1 (Con't)

CONDITION	--PRODUCT--		TEST SPECIMEN		YIELD		STRENGTH		WIDTH		SPECIMEN		CRACK		K(IIC) STAN		DATE	REFER
	FORM	THICK (IN)	THICK (IN)	ORIENT	(AST)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)		
BETA ANNEAL & STDA-1800F 0 5HR. AC. 1575F 0 5HR. WQ. 1050F 8 HR. AC	P	0.62	R	T	L-T	156.0	2.000	0.626	CT	1.000	0.27	51.30	50.1/	1.8	1974	88186		
RF. AB FOR-ANN BETA FLECTED. ALPHA-BETA FORGED. ANNEALED. 1350F 2 HR. AC	F	2.50	R	T	---	138.0	2.000	1.000	CT	1.000	0.73	74.50	73.3/	3.7	1974	88962		
RF. B FOR-ANN BETA FLECTED. ALPHA-BETA FORGED. ANNEALED. 1350F 2 HR. AC	F	2.50	R	T	---	136.0	2.000	1.000	CT	1.000	0.74	73.90	74.1/	0.5	1974	88962		
DE. LAB FOR-ANN BETA FLECTED. LOW ALPHA-BETA FORGED(11500F). ANNEALED. 1350F 2 HR. AC	F	2.50	R	T	---	141.0	2.000	1.000	CT	1.000	0.42	58.10	56.3/	1.6	1974	88962		
DUPLEX ANNEAL	P	0.50	R	T	T-L	150.5	2.000	0.500	CT	0.968	0.44	64.50	65.1/	2.0	1971	83222 (1)		
MILL ANNEALED	P	2.00	R	T	---	157.0	2.500	1.250	CT	1.250	0.18	42.30	42.3/	0.0	1973	90384 (2)		
MILL ANNEALED	P	1.00	R	T	T-L	151.3	2.530	1.000	WQL	---	0.20	42.80			1977	JEN01		

NOTES
 (1) 1700F 1 HR. ARGON COOL. 1400F 1 HR. ARGON COOL
 (2) COMPOSITION(WT PERCENT) 5 GAL. 5 4V. 2 OSN. 0 026C. 0 37FE. 0 014N. 0 084H. 0 180. 0 50CU

TABLE 4.13.2.1 (Con't)

CONDITION	TITANIUM		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	THICKNESS (IN)	DESIGN	CRACK LENGTH (IN)	2.5* K(1C)/TVS)**2 (IN)	K(1C) MEAN DEV (ABS) (IN)	K(1C) STAN DEV	DATE	REFER
	FORM	THICK (IN)											
MILL ANNEALED	P	0.50	R.T.	163.3	1.000	0.495	CT	0.517	0.10	33.20	35.0/	5.2	1971 83222
MILL ANNEALED	F	---	R.T.	144.0	2.500	1.250	CT	1.250	0.37	35.70	35.7/	0.1	1973 90584
MILL ANNEALED	F	3.80	65	165.0	2.502	1.007	CT	1.312	0.19	47.70	44.2/	5.7	1973 90589
MILL ANNEALED	F	3.80	R.T.	169.0	2.498	1.008	CT	1.299	0.19	47.20	47.20		1973 90589
MILL ANNEALED	F	3.80	R.T.	149.0	2.499	0.999	CT	1.297	0.43	61.70	61.70		1973 90589
MILL ANNEALED	F	3.80	R.T.	149.0	2.501	1.006	CT	1.300	0.36	56.90	56.90		1973 90589
MILL ANNEALED	F	3.80	R.T.	149.0	2.495	0.995	CT	1.301	0.37	57.30	58.6/	2.7	1973 90589
MILL ANNEALED	FB	1.50	R.T.	153.0	2.500	1.250	CT	1.250	0.20	43.10	43.10		1973 90584
MILL ANNEALED	BT	2.20	R.T.	144.0	2.500	1.251	CT	1.332	0.37	55.60	55.60		1971 84360
MILL ANNEALED	BT	2.20	R.T.	144.0	2.507	1.243	CT	1.262	0.42	58.90	58.90		1971 84360
MILL ANNEALED	BT	2.20	R.T.	146.0	2.500	1.243	CT	1.216	0.30	50.40	50.40		1971 84360
MILL ANNEALED	BT	2.20	R.T.	146.0	2.495	1.233	CT	1.297	0.23	44.30	52.3/	6.4	1971 84360
MILL ANNEALED	BT	2.20	R.T.	155.0	2.495	1.235	CT	1.295	0.32	55.50	55.50		1971 84360
MILL ANNEALED	BT	2.20	R.T.	155.0	2.500	1.254	CT	1.254	0.36	58.60	57.1/	2.2	1971 84360
RECRYSTALLIZE ANNEAL	P	1.00	R.T.	150.0	2.550	1.000	MOL	----	0.45	63.70	63.70		1977 JEM01
STA-1600F 0 HR. MO. 1000F 6 HR. AC	F	3.80	65	209.0	2.474	1.010	CT	1.326	0.05	20.70	20.70		1973 90589
STA-1600F 0 HR. MO. 1000F 6 HR. AC	F	3.80	R.T.	209.0	2.499	1.005	CT	1.267	0.05	28.80	28.80		1973 90589
STA-1600F 0 HR. MO. 1000F 6 HR. AC	F	3.80	R.T.	209.0	2.476	1.007	CT	1.283	0.04	27.80	28.4/	0.6	1973 90589
STA-1600F 0 HR. MO. 1000F 6 HR. AC	F	3.80	R.T.	184.0	2.478	1.005	CT	1.290	0.07	31.40	31.40		1973 90589
STA-1600F 0 HR. MO. 1000F 6 HR. AC	F	3.80	R.T.	184.0	2.502	1.006	CT	1.296	0.07	30.20	30.20		1973 90589
STA-1600F 0 HR. MO. 1000F 6 HR. AC	F	3.80	R.T.	184.0	2.501	1.007	CT	1.278	0.07	30.60	30.8/	0.7	1973 90589
STA-1600F 0 HR. MO. 1000F 6 HR. AC	F	3.80	300	165.0	2.501	1.001	CT	1.292	0.28	55.50	55.50		1973 90589

TABLE 4.13.2.1 (Con't)

CONDITION	TITANIUM										K(IIC) STAN	DATE	REFER
	--PRIME--		TEST SPECIMEN		SPECIMEN		CRACK		K(IIC) MEAN DEV				
	FORM	THICK (IN)	THICK (IN)	ORIENT	YIELD (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	LENGTH (IN)	2.5* (K(IIC)/TYS)**2 (IN)			
STA-1650F 0.5HR. WQ. 1000F 6 HR. AC	F	3.00	300	L-T	165.0	2.497	1.015	CT	1.278	0.27	54.20	1973 90589	
		3.00			165.0	2.479	1.009	CT	1.272	0.22	47.40	1973 90589	
STA-1650F 0.5HR. WQ. 1000F 24 HR. AC	F		R.T.	L-C	188.0	0.998	0.500	CT	0.508	0.04	24.60	1972 86494 (1)	
					188.0	0.994	0.500	CT	0.507	0.04	24.50	1972 86494 (1)	
					188.0	0.997	0.498	CT	0.532	0.03	23.50	1972 86494 (1)	
					188.0	1.000	0.499	CT	0.536	0.03	23.60	1972 86494 (1)	
STA-1650F 0.5HR. WQ. 1000F 24 HR. AC	F		R.T.	C-L	188.0	1.005	0.500	CT	0.517	0.06	29.10	1972 86494 (1)	
					188.0	1.001	0.500	CT	0.523	0.05	29.60	1972 86494 (1)	
					188.0	1.001	0.500	CT	0.505	0.05	29.30	1972 86494 (1)	
STA-1675F 0.25 HR. WQ. 1100F 4 HR	P	1.25	R.T.	T-L	173.3	2.000	0.499	CT	1.080	0.11	37.00	1971 83222	
		1.25			173.3	2.000	0.499	CT	1.138	0.07	29.80	1971 83222	
		1.25			173.3	2.000	0.499	CT	1.046	0.10	33.50	1971 83222	
STA-1600F 1 HR. WQ. 1200F 6 HR. AC	E	3.00	R.T.	C-R	143.0	1.476	0.750	CT	0.779	0.36	54.20	1973 87230 (2)	
		3.00			143.0	1.408	0.750	CT	0.808	0.33	52.00	1973 87230 (2)	
		3.00			143.0	1.479	0.749	CT	0.783	0.34	54.50	1973 87230 (2)	
STA-1650F 1 HR. WQ. 1300F 2 HR. AC	F	2.50	R.T.		154.0	2.000	1.000	CT	1.000	0.18	41.60	1974 88962	
		2.50			154.0	2.000	1.000	CT	1.000	0.17	40.40	1974 88962	
STA-1700F 1 HR. WQ. 1400F 1 HR. AC	P	0.38	R.T.	L-T	156.0	1.000	0.375	CT		0.20	44.30	1974 90981	
		0.38			156.0	1.000	0.375	CT		0.18	41.90	1974 90981	
		0.38			156.0	1.000	0.375	CT		0.18	42.50	1974 90981	

NOTES
 (1) ISOTHERMAL FORGING FOR AIRCRAFT NOSE WHEEL
 (2) ALPHA PRECIPITATE IN BETA MATRIX
 STRAIGHTNESS OF CRACK FRONT MAY NOT MEET ASIN E399-72 REQUIREMENTS

TABLE 4.13.2.1 (Con't)

CONDITION	TITANIUM										K(1C) STAN DEV	DATE	REFER
	11-6AL-6V-2SN		K(1C)		SPECIMEN		CRACK		2.9				
	FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	LENGTH (IN)	K(1C)/TVB			
S10A-1700F 1 HR. HQ. 140HF 1 HR. AC	P	0.38	R.T.	T-I	160.0	1.000	0.375	CT	---	0.19	44.00	1974	90981
		0.38			160.0	1.000	0.375	CT	---	0.23	48.30	1974	90981
		0.38			160.0	1.000	0.375	CT	---	0.18	42.90	1974	90981
S10A-1700F 1 HR. HQ. 140HF 1 HR. AC	BT	12.00	R.T.	L-T	147.0	2.000	1.020	NB	---	0.33	53.60	1974	90981
		12.00			147.0	2.000	1.020	NB	---	0.37	70.40	1974	90981
		12.00			148.0	2.000	1.020	NB	---	0.46	63.70	1974	90981
S10A-1700F 1 HR. HQ. 140HF 1 HR. AC	BT	12.00	R.T.	L-T	148.0	2.000	1.020	NB	---	0.46	63.40	1974	90981
		12.00			144.0	2.000	1.020	NB	---	0.42	58.80	1974	90981
		12.00			144.0	2.000	1.020	NB	---	0.40	58.00	1974	90981
1650F 1 HR. HQ. 1050F 1 HR. AC	F	4.50	-320	L-C	270.0	0.501	0.250	NB	0.122	0.02	22.60	1965	84316
		4.50			270.0	0.978	0.501	NB	0.193	0.02	24.50	1965	84316
		4.50	R.T.	L-C	184.0	0.978	0.501	NB	0.191	0.06	27.80	1965	84316
1650F 1 HR. HQ. 1050F 1 HR. AC	F	4.50	R.T.	L-C	184.0	0.978	0.501	NB	0.301	0.07	31.40	1965	84316
		4.50			184.0	0.501	0.251	NB	0.177	0.07	30.40	1965	84316
		4.50			184.0	0.978	0.502	NB	0.274	0.08	32.40	1965	84316
1675F 2 HR. AC 1600F 1 HR. FC	P	2.00	R.T.	---	150.0	2.500	1.250	CT	1.250	0.34	55.00	1973	90384 (1)
		2.00			150.0	2.500	1.250	CT	1.250	0.30	52.50	1973	90384 (1)
		---	R.T.	---	138.0	2.500	1.250	CT	1.250	0.46	58.90	1973	90384
1675F 2 HR. AC 1600F 1 HR. FC	F	1.50	R.T.	---	150.0	2.500	1.250	CT	1.250	0.43	62.20	1973	90384
		1.50			150.0	2.500	1.250	CT	1.250	0.38	58.20	1973	90384
		---			138.0	2.500	1.250	CT	1.250	0.46	58.90	1973	90384

NOTES
(1) COMPOSITION (WT PERCENT) 5.6AL, 3.4V, 2.0SN, 0.02AC, 0.57FE, 0.014N, 0.004H, 0.18D, 0.50CU

TABLE 4.13.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-6AL-6V-2SN
CONDITION: BA
ENVIRONMENT: R. T. , HUMID AIR

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	R=+0.10			
DELTA K A:				
MIN B:				
C:				
D:				
200.00 :				
DELTA K A:				
MAX B:				
C:				
D:				
ROOT MEAN SQUARE	0.00			
PERCENT ERROR				

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: BA
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., HUMID AIR

YIELD STRENGTH: 130.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.375"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90001

TITAN.
 ALLOY

TI-6AL-
 6V-2SN

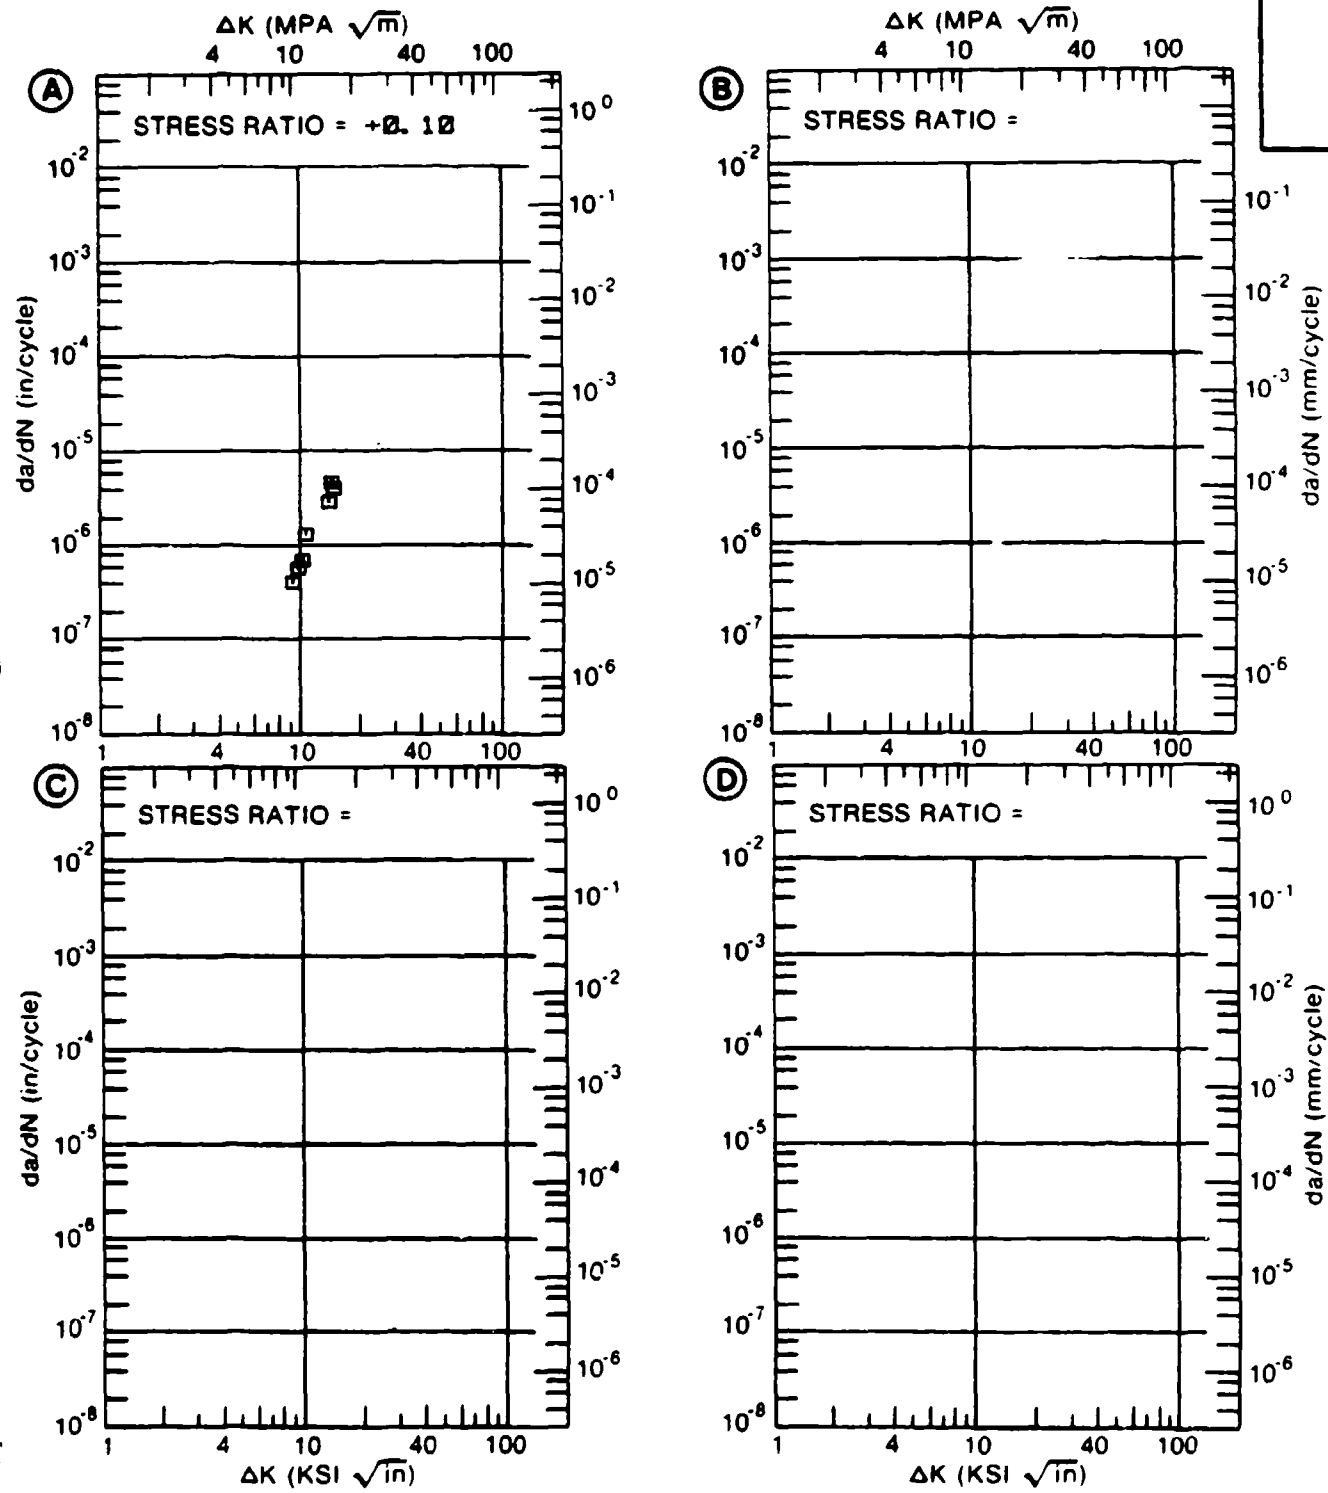


Figure 4.13.3.1

TABLE 4.13.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: BA

TI-6AL-6V-2SN

DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. 3.5% NAACL			
DELTA K MIN	A:	8.91	1.38		
	B:				
	C:				
	D:				
		9.00	1.36		
		10.00	1.51		
		13.00	5.40		
		16.00	12.5		
DELTA K MAX	A:	17.76	12.0		
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 27.07
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: BA
 FORM: 0.39" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 STRESS RATIO: +0.10
 FREQUENCY: 0.10- 10.00 HZ

YIELD STRENGTH: 180.0 KSI
 ULT. STRENGTH: 188.0 KSI
 SPECIMEN THK: 0.375"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90001

TITAN.
 ALLOY
 TI-6AL-
 6V-2SN

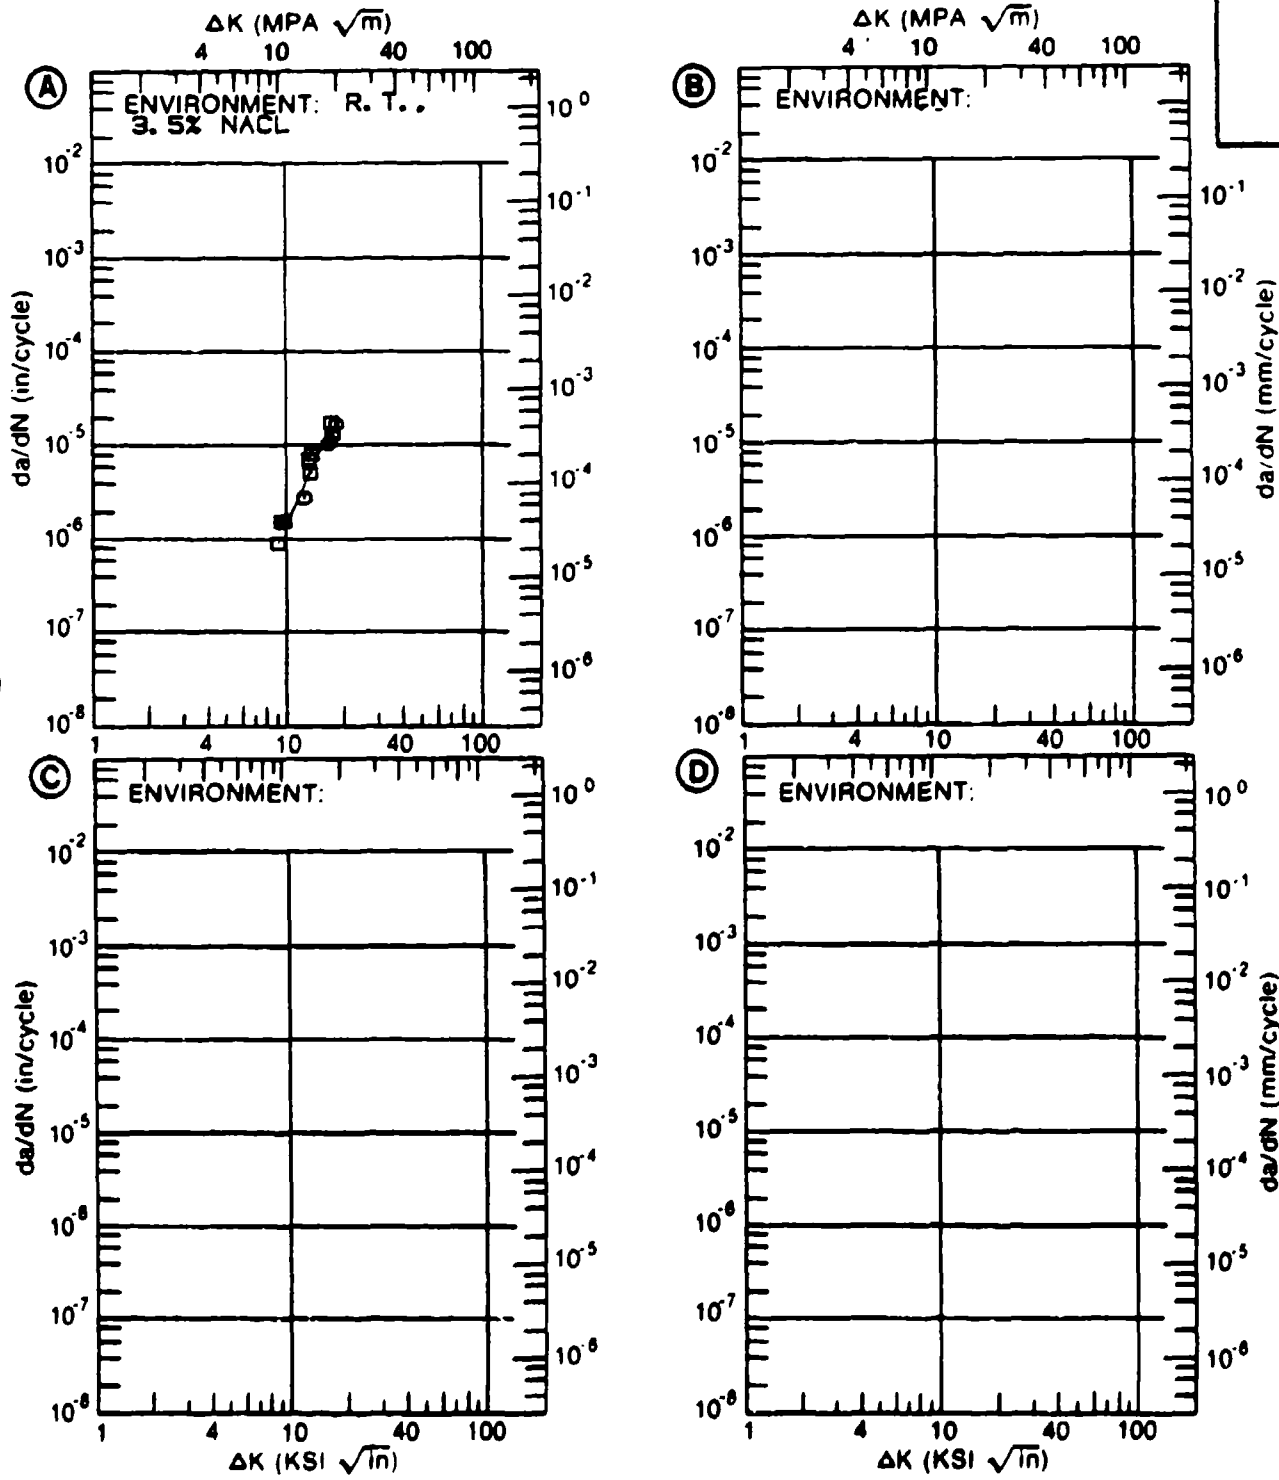


Figure 4.13.3.2

TABLE 4.13.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: MA

TI-6AL-6V-2SN

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E= R. T. INTERSTITIAL OXYGEN=0.08%		E= R. T. INTERSTITIAL OXYGEN=0.16%	
DELTA K MIN	A: 16.07	3.37	B: 8.57	
	B: 18.53			
	C:			
	D:			
	20.00	9.21	11.7	
	25.00	17.8	30.7	
	30.00	26.7	66.7	
	35.00	37.7		
	40.00	53.5		
DELTA K MAX	A: 49.10	112.	B: 171.	
	B: 31.63			
	C:			
	D:			
ROOT MEAN SQUARE PERCENT ERROR		5.19	12.71	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5			
	0.5-0.8			
	0.8-1.25			
	1.25-2.0			
	>2.0			

CONDITION/HT: MA
 FORM:
 SPECIMEN TYPE:
 ORIENTATION:
 STRESS RATIO:
 FREQUENCY:

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 91945

TITAN.
 ALLOY

TI-6AL-
 2V-2SN

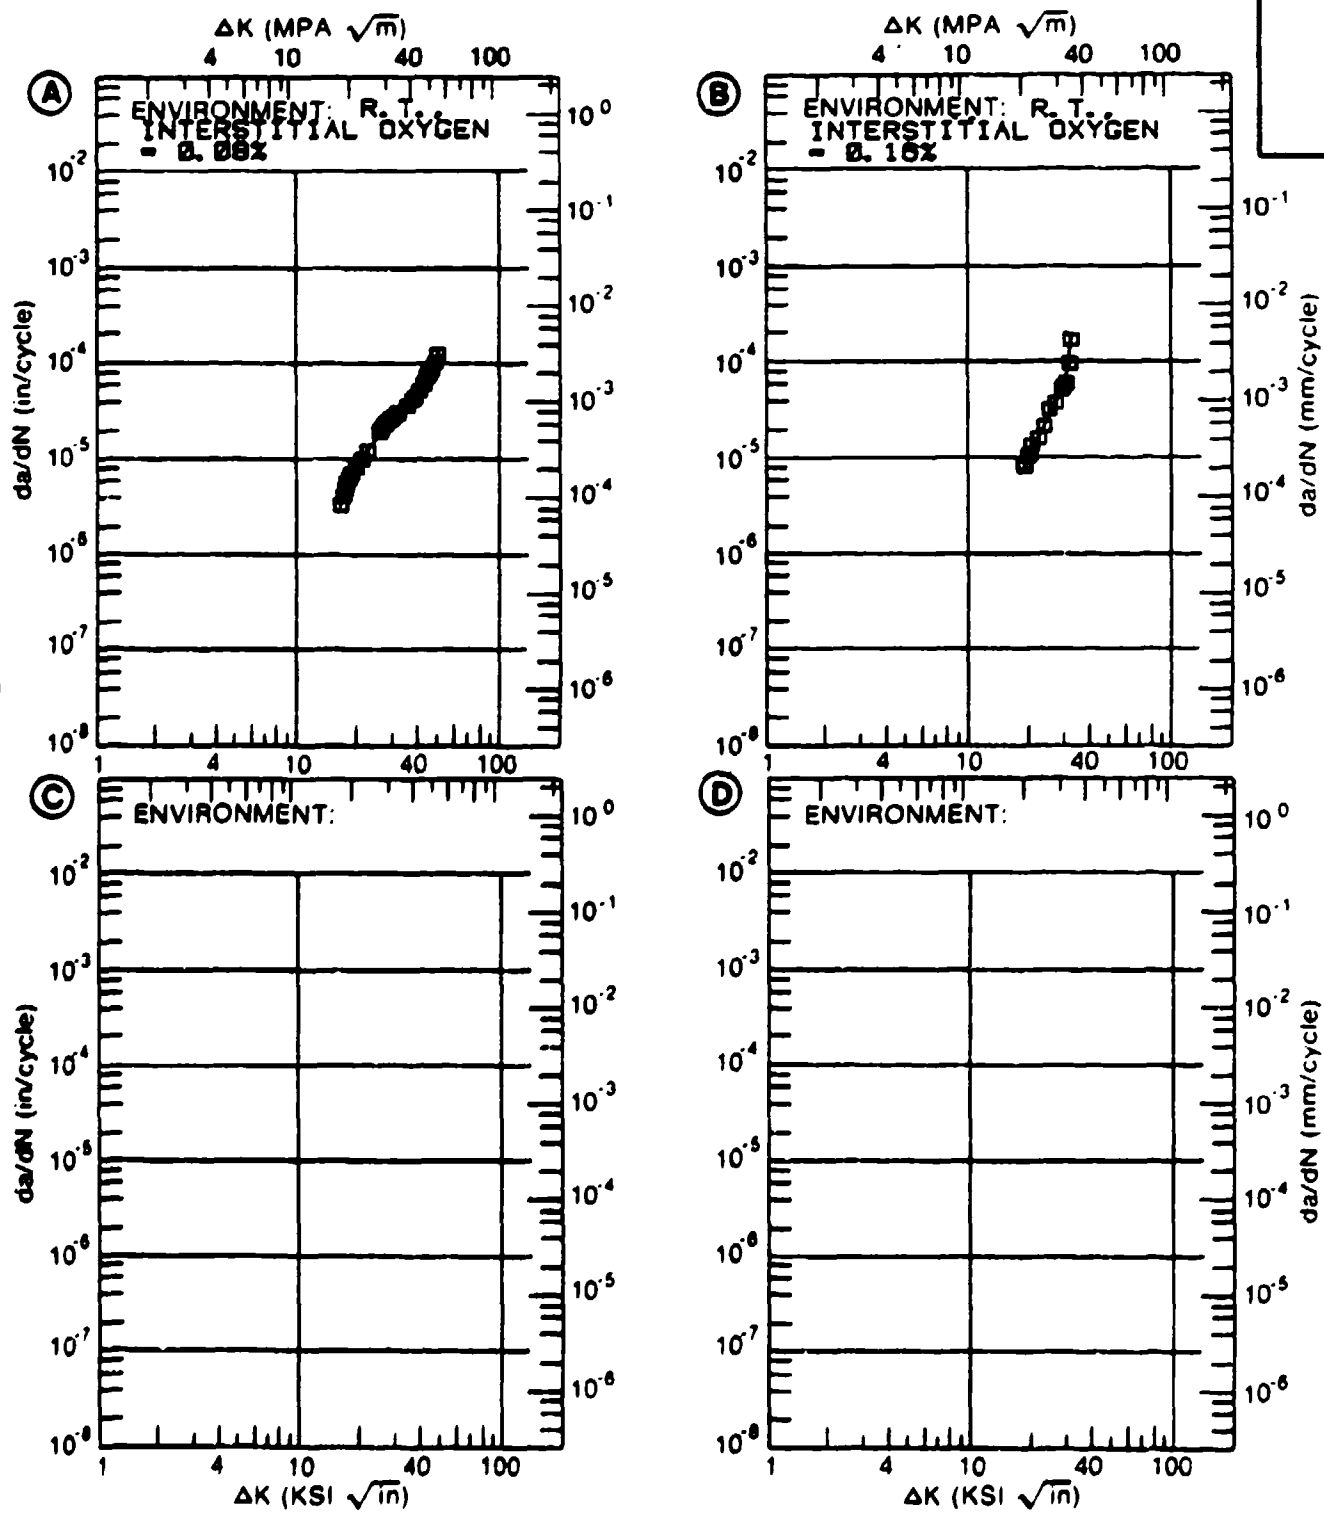


Figure 4.13.3.3

TABLE 4.13.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.4 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: MA

TI-6AL-6V-2SN

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K	A: 4.16	.0207			
MIN	B:				
	C:				
	D:				
	5.00	.0440			
	6.00	.0905			
	7.00	.164			
	8.00	.271			
	9.00	.420			
	10.00	.620			
	13.00	1.61			
	16.00	3.43			
	20.00	7.73			
	25.00	17.7			
	30.00	35.2			
	35.00	64.0			
	40.00	109.			
DELTA K	A: 41.81	130.			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 19.73
PERCENT ERROR

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	1
RATIO	0.8-1.25	1
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: MA
 FORM: EXTRUSION
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.02
 FREQUENCY: 0.10- 20.00 HZ

YIELD STRENGTH: 143.0 KSI
 ULT. STRENGTH: 157.0 KSI
 SPECIMEN THK: 0.081- 0.082"
 SPECIMEN WIDTH: 3.509- 3.519"
 REFERENCES: MA002

TITAN.
 ALLOY

TI-6AL-
 6V-2SN

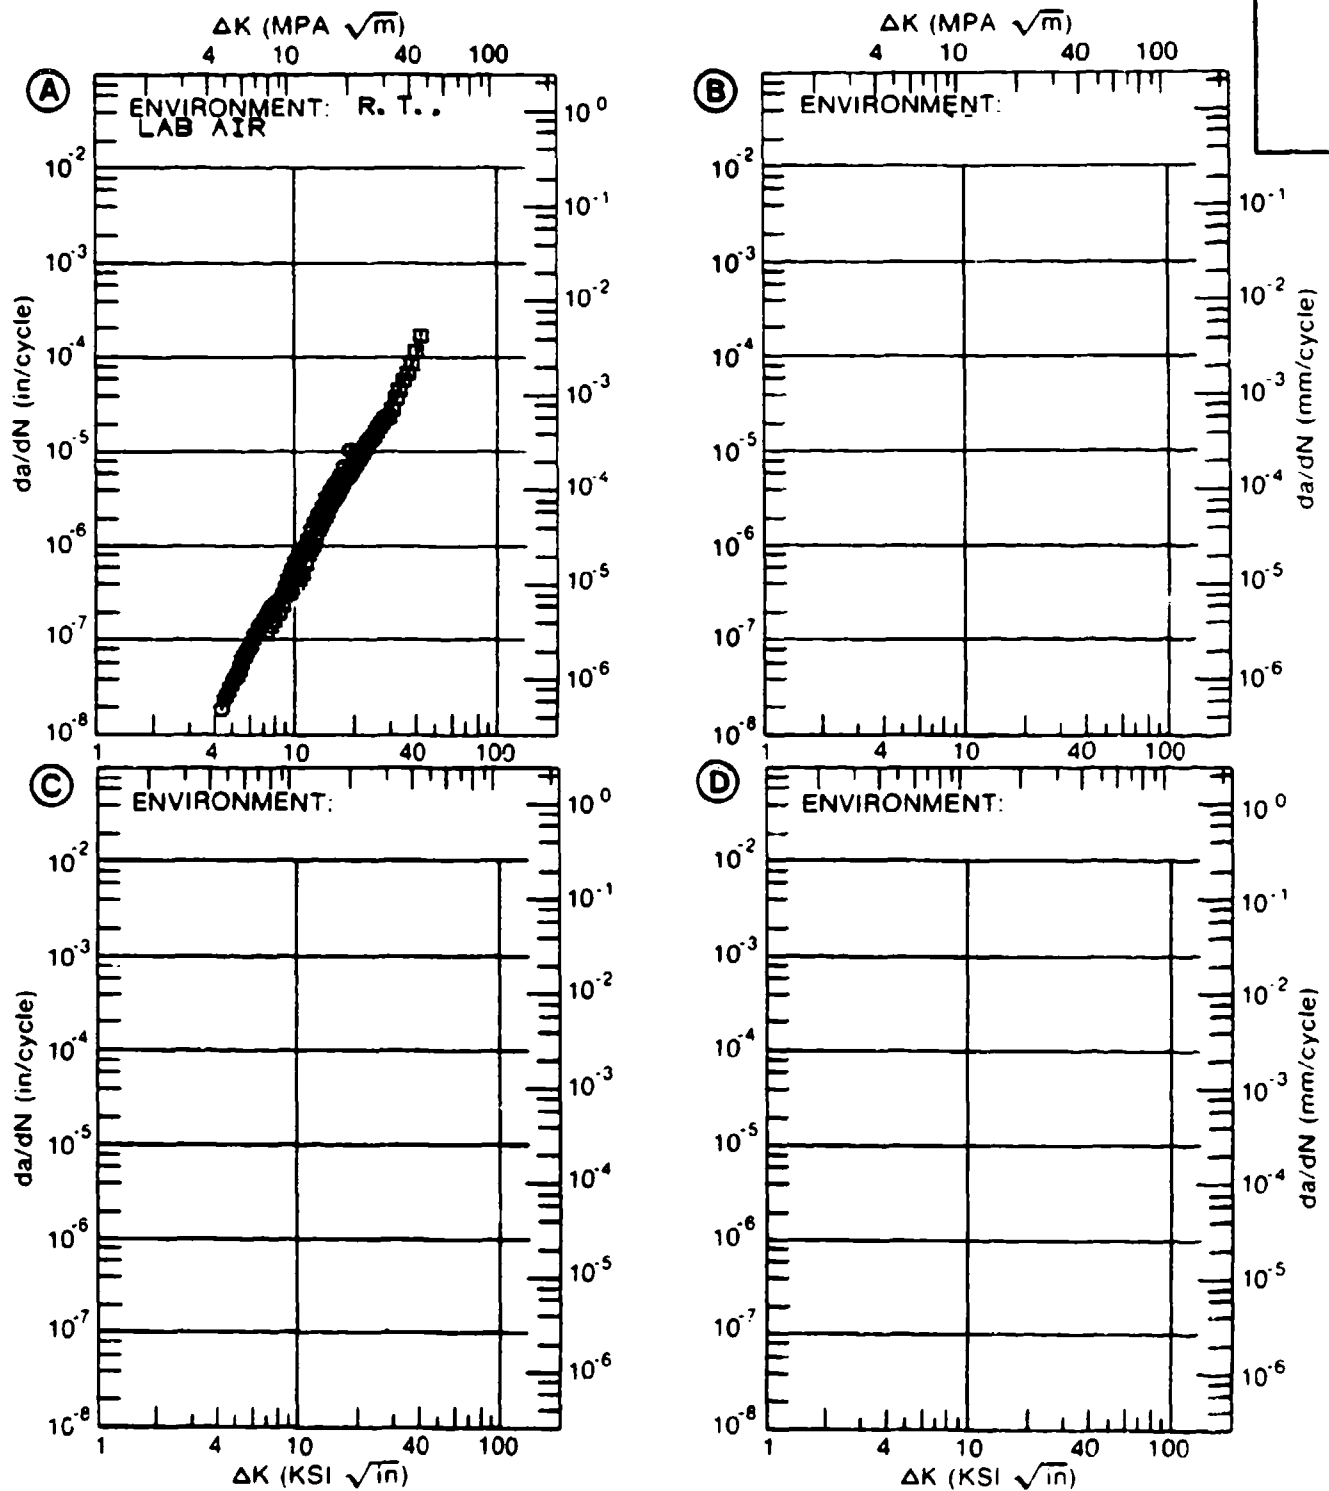


Figure 4.13.3.4

TABLE 4.13.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.5 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-6V-2SN			
CONDITION: MA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY ARGON	E= R. T. DRY AIR	E= R. T. JP-4 FUEL	E= R. T. DIST. WATER
DELTA K	A: 13.02	4.85			
MIN	B: 10.24		1.28		
	C: 10.06			2.41	
	D: 10.25				.93
	13.00		3.53	5.70	2.36
	16.00	6.20	7.54	10.9	4.79
	20.00	10.3	11.1	22.4	9.77
	25.00	21.0	19.1	51.6	17.9
	30.00	40.9	48.9	118.	36.9
	35.00	72.9	107.	271.	65.4
	40.00	120.	164.	632.	113.
	50.00	633.	391.		322.
DELTA K	A: 55.28	911.			
MAX	B: 58.24		1749.		
	C: 42.78			1015.	
	D: 58.29				747.
ROOT MEAN SQUARE		23.61	29.90	21.93	25.52
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: MA
 FORM: 2.00" TH FORGING
 SPECIMEN TYPE: DCB
 ORIENTATION: L-T
 STRESS RATIO: +0.02
 FREQUENCY: 0.00- 10.00 HZ

YIELD STRENGTH: 144.0- 155.0 KSI
 ULT. STRENGTH: 151.0- 164.0 KSI
 SPECIMEN THK: 0.750"
 SPECIMEN WIDTH: 5.500"
 REFERENCES: 04300

TITAN.
 ALLOY

TI-6AL-
 6V-2SN

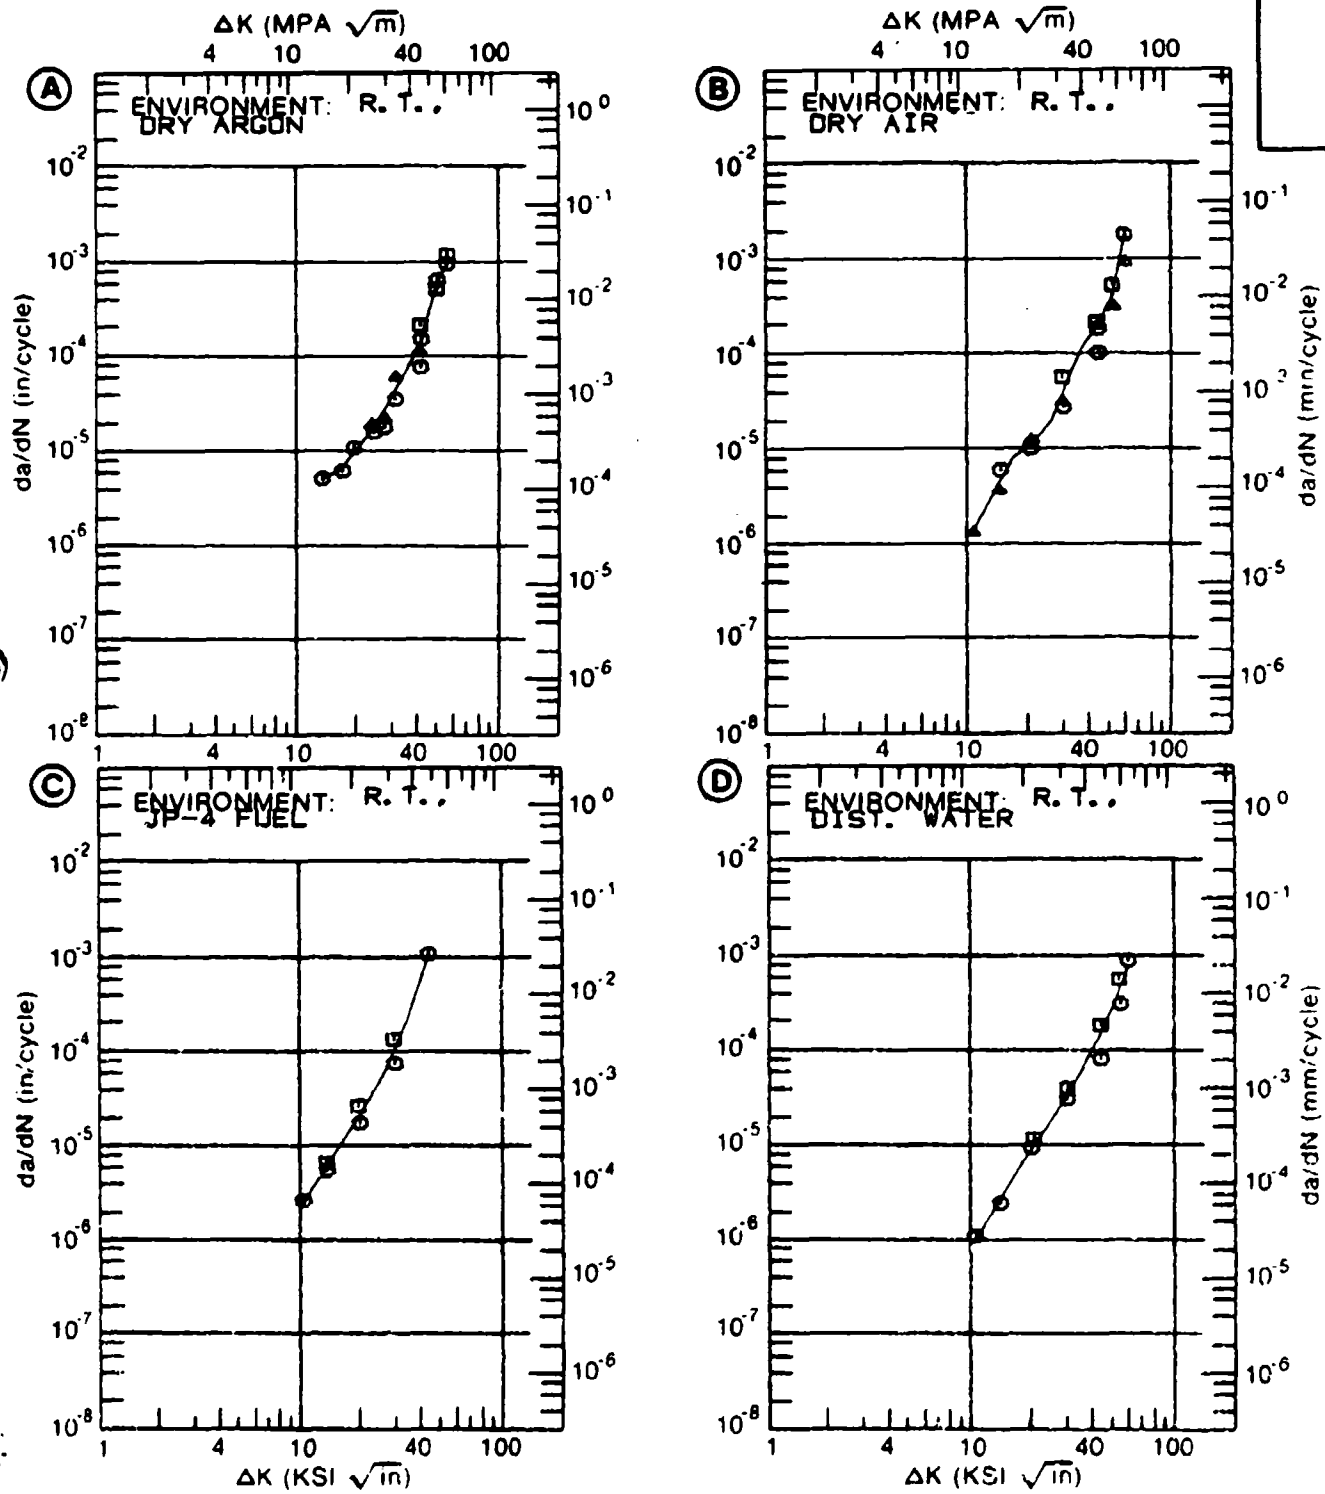


Figure 4.13.3.5

TABLE 4.13.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.6 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-6V-2SN			
CONDITION: RA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. INTERSTITIAL OXYGEN=0.08%	E= R. T. INTERSTITIAL OXYGEN=0.16%		
DELTA K	A: 18.44	4.64			
MIN	B: 21.24		10.6		
	C:				
	D:				
	20.00	6.36			
	25.00	13.6	23.7		
	30.00	23.0	47.1		
	35.00	34.8	72.4		
	40.00	49.3	96.3		
	50.00	86.0			
	60.00	125.			
	70.00	154.			
	80.00	176.			
	90.00	195.			
DELTA K	A: 91.66	199.			
MAX	B: 48.09		129.		
	C:				
	D:				
ROOT MEAN SQUARE		10.65	7.01		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: RA
 FORM:
 SPECIMEN TYPE:
 ORIENTATION:
 STRESS RATIO:
 FREQUENCY:

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 91845

TITAN.
 ALLOY

TI-8AL-
 6V-2SN

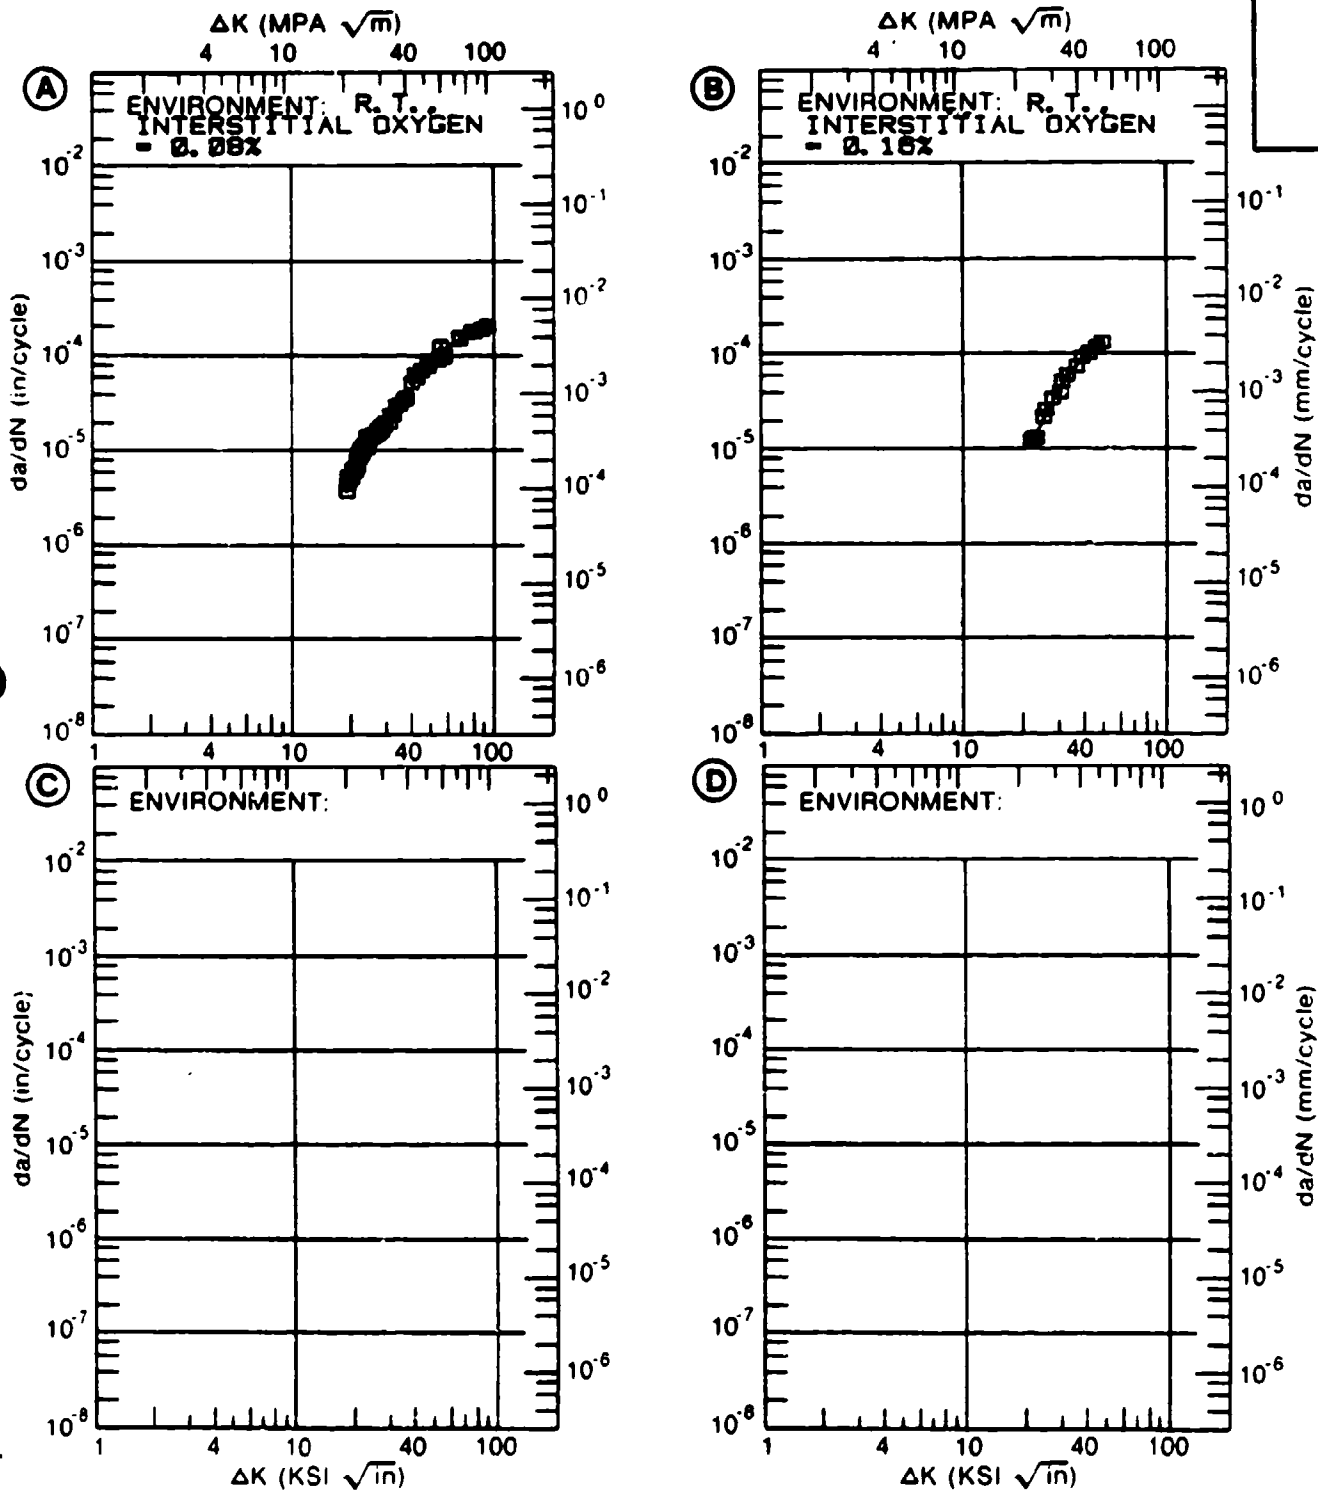


Figure 4.13.3.6

TABLE 4.13.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.13.3.7 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-6V-29N			
CONDITION: STOA					
ENVIRONMENT: R. T. , HUMID AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K A:	8.20	.39			
MIN B:					
C:					
D:					
	9.00	.525			
	10.00	.734			
	13.00	1.67			
	16.00	3.15			
	20.00	5.98			
	25.00	10.8			
	30.00	16.7			
	35.00	23.2			
	40.00	29.9			
	50.00	42.3			
DELTA K A:	54.31	46.9			
MAX B:					
C:					
D:					
ROOT MEAN SQUARE		33.44			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: STDA
 FORM: 0.13" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., HUMID AIR

YIELD STRENGTH: 137.4 KSI
 ULT. STRENGTH: 143.0 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 00001

TITAN.
 ALLOY

TI-6AL-
 4V-2SN

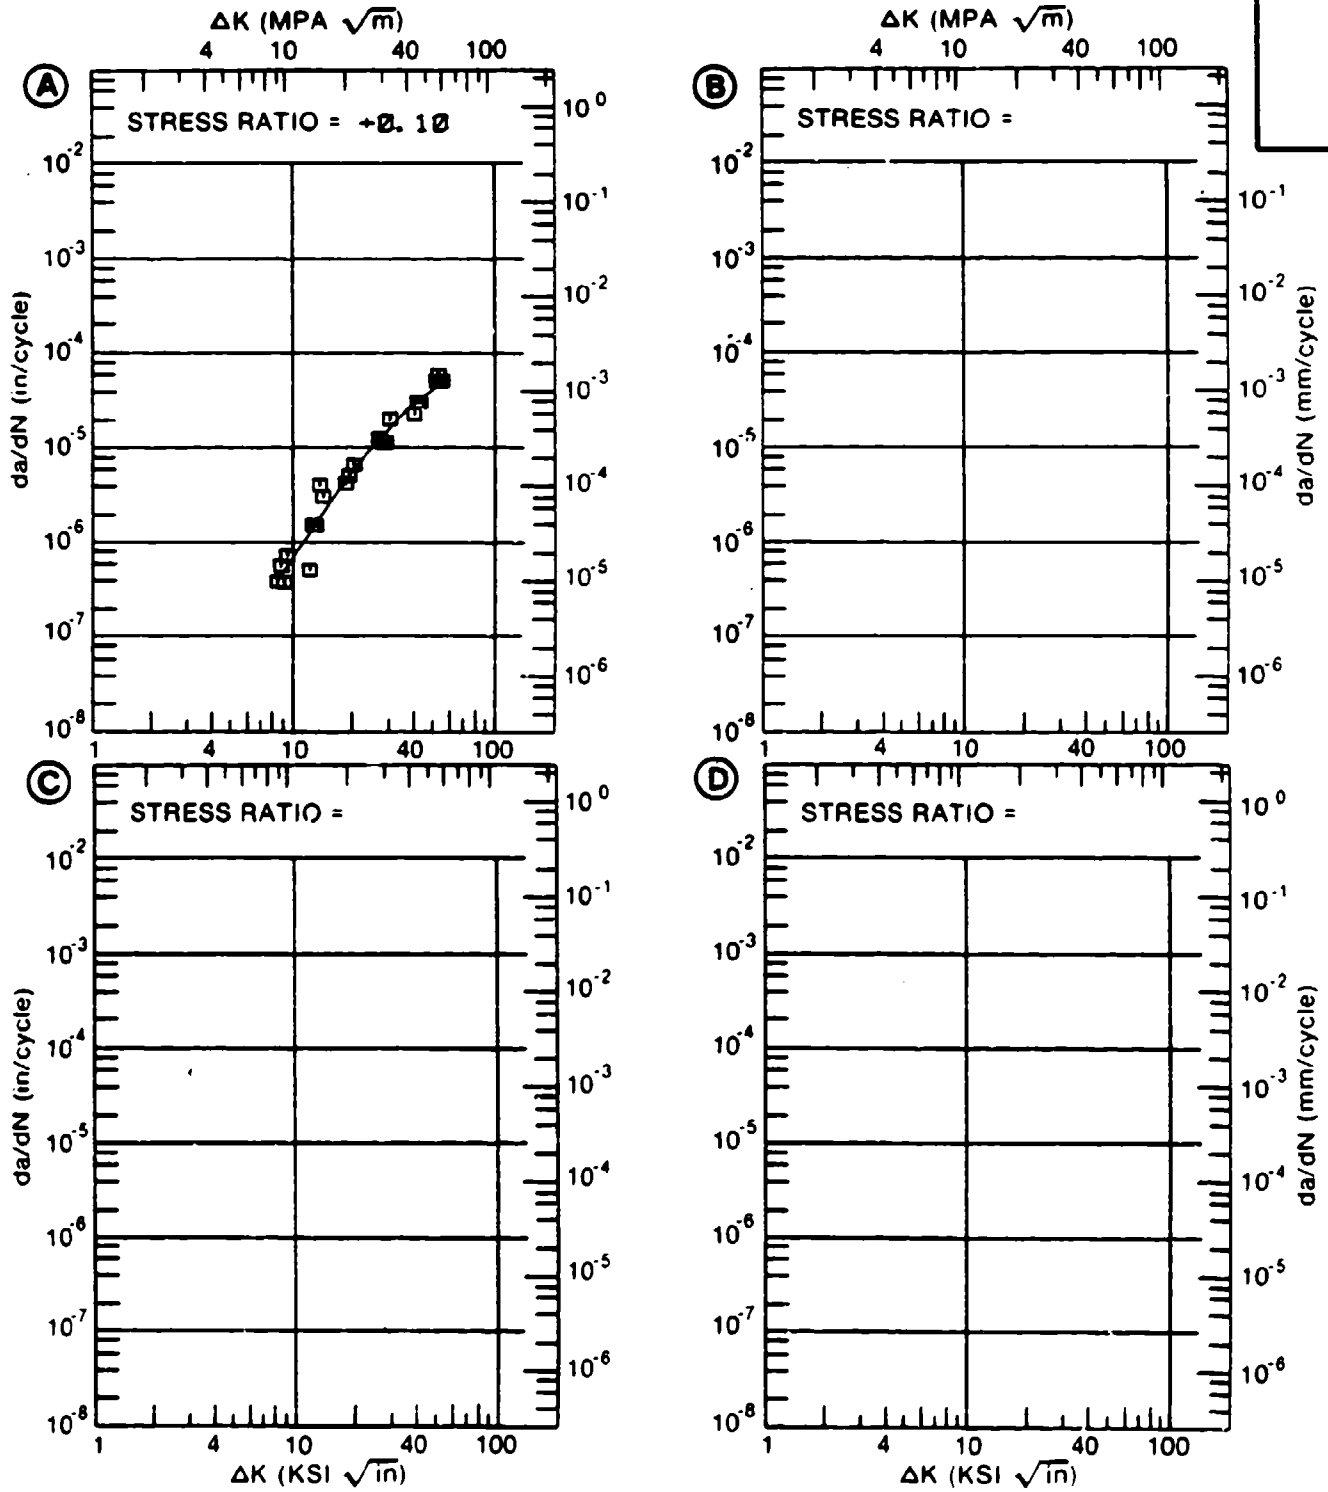


Figure 4.13.3.7

TABLE 4.13.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.8 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-6V-2SN			
CONDITION: STOA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. H. H. A.	E= R. T. 3. 5% NACL		
DELTA K	A: 9.04	. 526			
MIN	B: 8.98		2. 50		
	C:				
	D:				
	9.00		2. 48		
	10.00	2. 58	3. 14		
	13.00	4. 48	15. 0		
	16.00	5. 34	20. 8		
	20.00	9. 03	29. 2		
	25.00	20. 5	53. 7		
	30.00	47. 9	61. 1		
	35.00	104.			
DELTA K	A: 39.96	140.			
MAX	B: 30.00		61. 1		
	C:				
	D:				
ROOT MEAN SQUARE		12. 68	8. 44		
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25				
SUMMARY	1. 25-2. 0				
(NP/NA)	>2. 0				

CONDITION/HT: STOA
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: L-S
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH: 130.0 KSI
 ULT. STRENGTH: 167.2 KSI
 SPECIMEN THK: 0.373- 0.374"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90981

TITAN.
 ALLOY

TI-6AL-
 6V-2SN

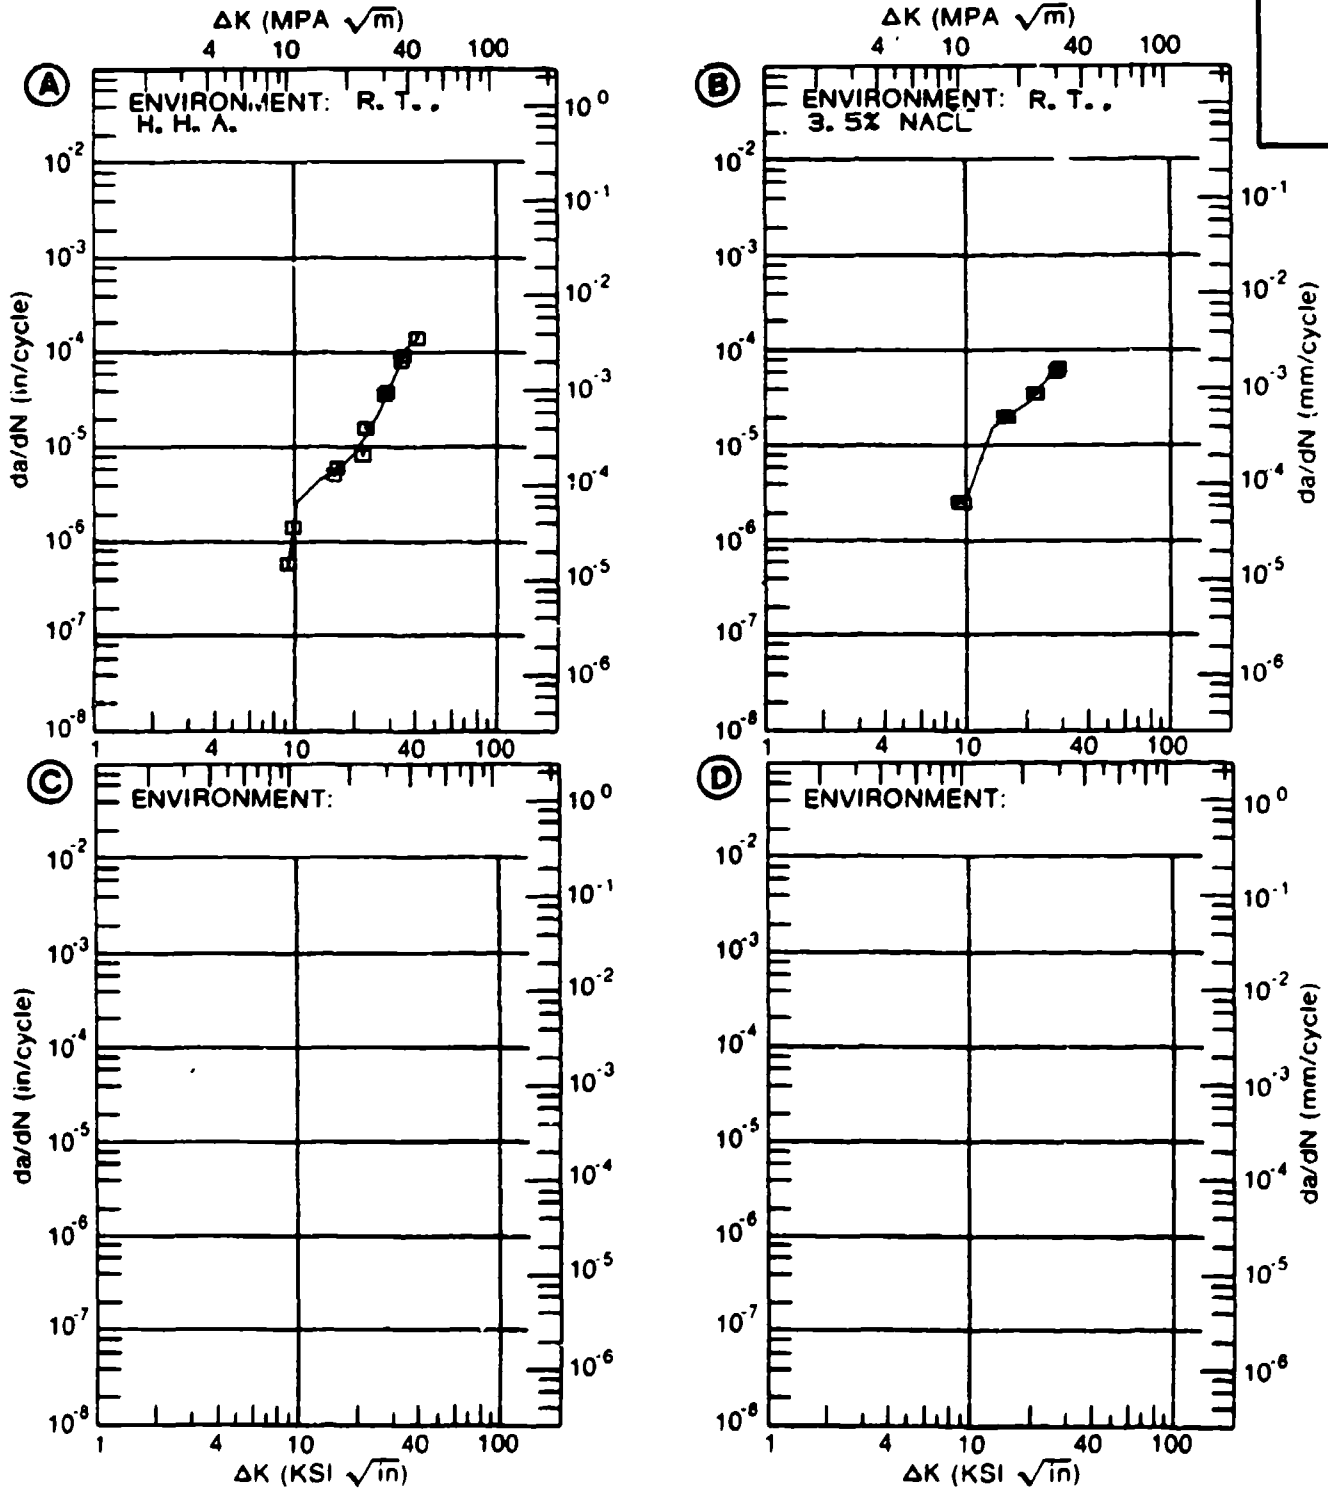


Figure 4.13.3.8

TABLE 4.13.3.9

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.9 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-6V-2SN			
CONDITION: STOA					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		H. H. A.			
DELTA K	A: 8.70	.824			
MIN	B:				
	C:				
	D:				
	9.00	1.01			
	10.00	1.73			
	13.00	4.16			
	16.00	6.42			
	20.00	10.2			
	25.00	20.7			
	30.00	53.0			
DELTA K	A: 34.23	139.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		16.00			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: ST0A
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: L-S
 STRESS RATIO: +0.10
 FREQUENCY: 0.10 HZ

YIELD STRENGTH: 130.0 KSI
 ULT. STRENGTH: 187.2 KSI
 SPECIMEN THK: 0.372"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 00001

TITAN.
 ALLOY

TI-6AL-
 6V-2SN

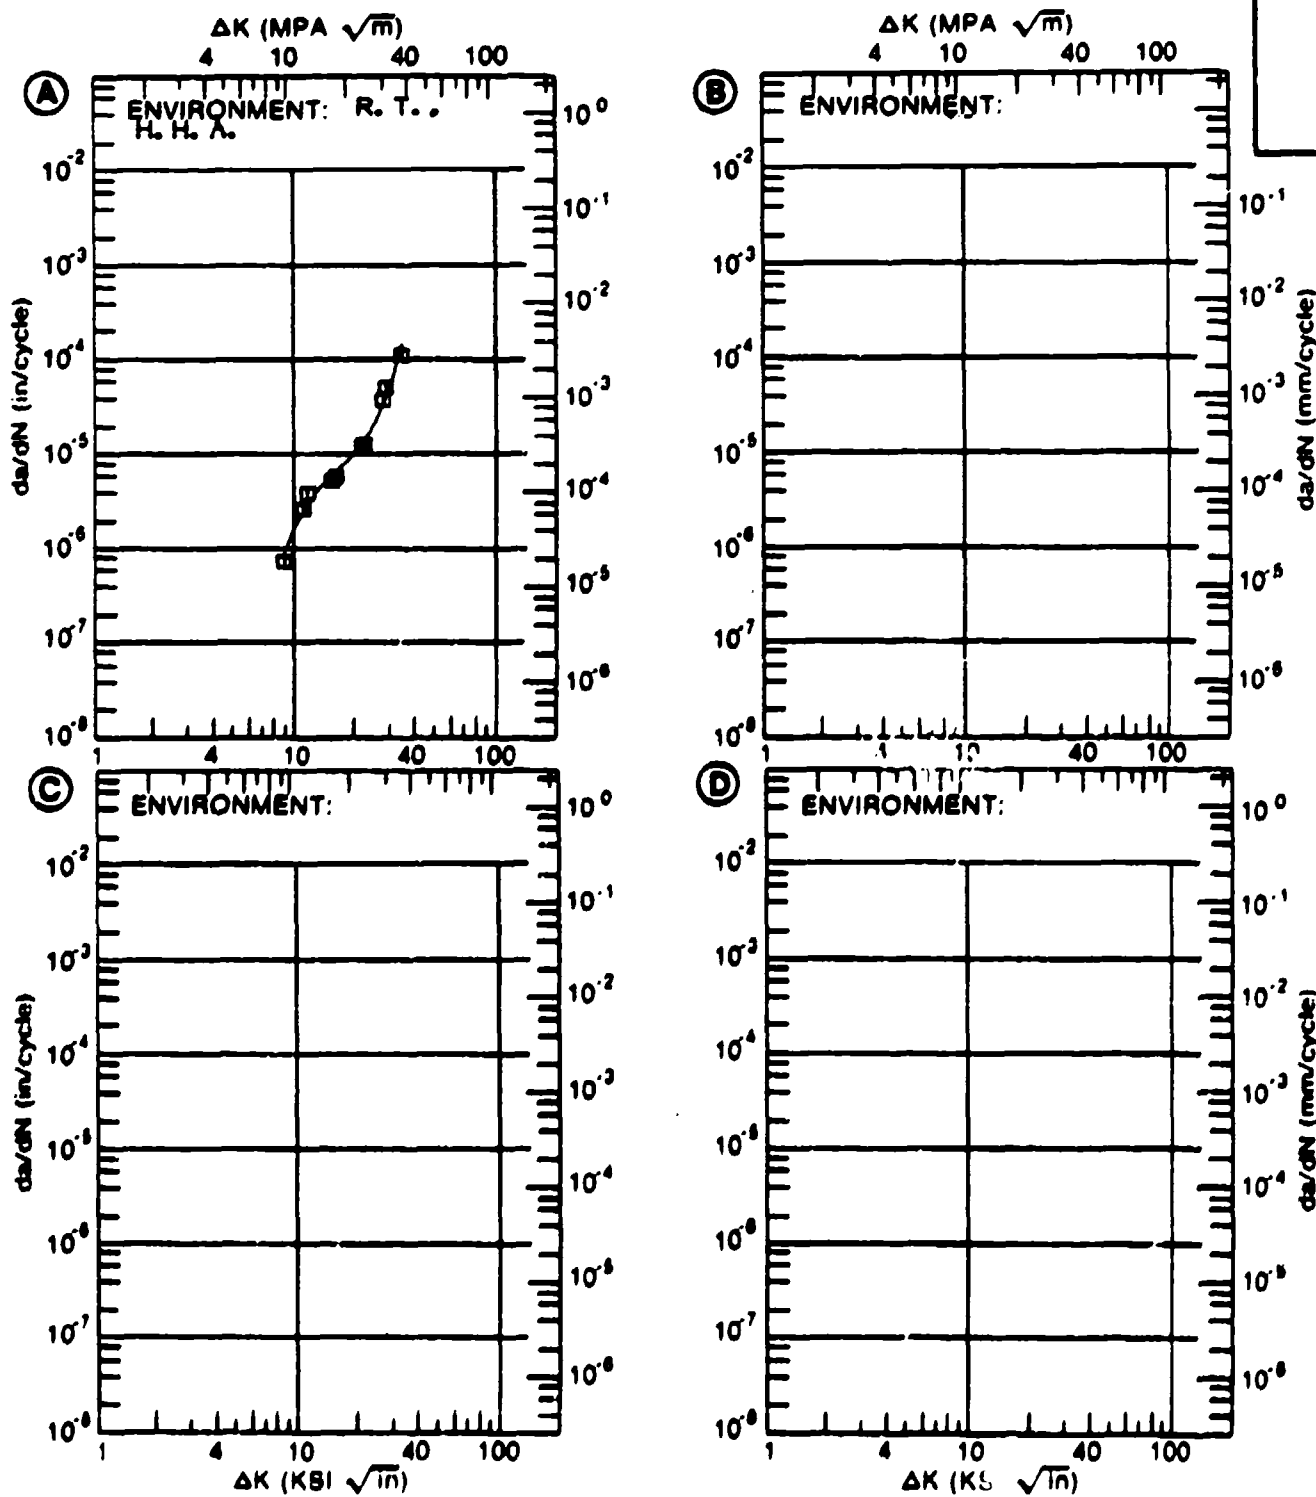


Figure 4.13.3.9

TABLE 4.13.3.10

**FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR**

**DATA ASSOCIATED WITH FIGURE 4.13.3.10 INDICATING EFFECT
OF STRESS RATIO**

MATERIAL: TITANIUM		TI-6AL-6V-2SN			
CONDITION: STCA					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K MIN	A: 8.60	.537			
	B: 8.90		1.35		
	C:				
	D:				
	9.00	.670	1.45		
	10.00	1.15	2.67		
	13.00	4.83	11.7		
16.00	14.7	31.4			
20.00	41.6	63.5			
25.00	88.0				
30.00	119.				
DELTA K MAX	A: 33.13	122.			
	B: 22.70		75.8		
	C:				
	D:				
ROOT MEAN SQUARE		45.83	36.19		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: ST0A
 FORM: 0.30" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 FREQUENCY: 0.10 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 130.0 KSI
 ULT. STRENGTH: 187.2 KSI
 SPECIMEN THK: 0.373- 0.374"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 00001

TITAN.
 ALLOY

TI-6AL-
 4V-2SN

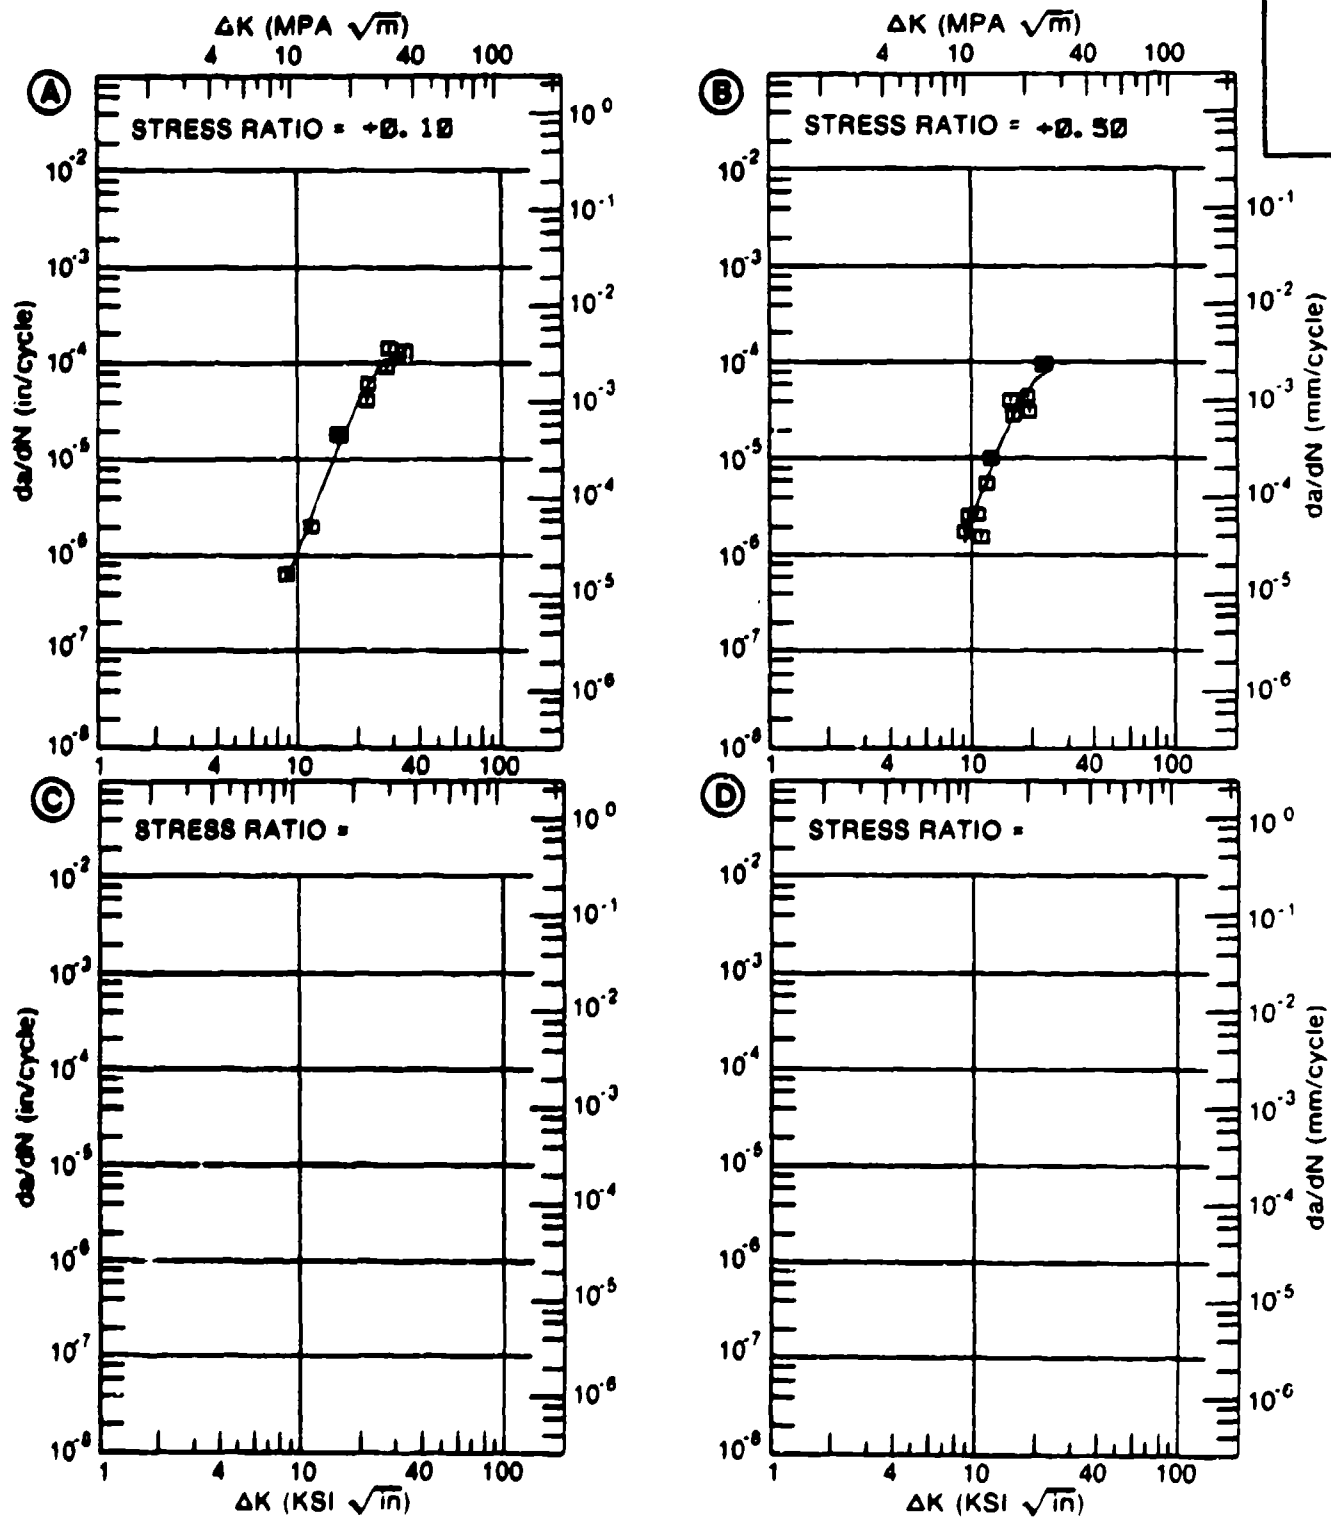


Figure 4.13.3.10

TABLE 4.13.3.11

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.11 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-6V-2SN			
CONDITION: STOA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T.			
		3. 5% NACL			
DELTA K	A: 9. 26	1. 28			
MIN	B:				
	C:				
	D:				
	10. 00	1. 49			
	13. 00	6. 18			
	16. 00	27. 2			
	20. 00	92. 1			
	25. 00	185.			
	30. 00	282.			
	35. 00	423.			
	40. 00	685.			
DELTA K	A: 45. 85	2081.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		32. 03			
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25				
SUMMARY	1. 25-2. 0				
(NP/NA)	>2. 0				

CONDITION/HT: ST0A
 FORM: 0.98" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 STRESS RATIO: +0.10
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 156.5 KSI
 ULT. STRENGTH: 187.8 KSI
 SPECIMEN THK: 0.375"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90981

TITAN.
 ALLOY
 TI-6AL-
 6V-2SN

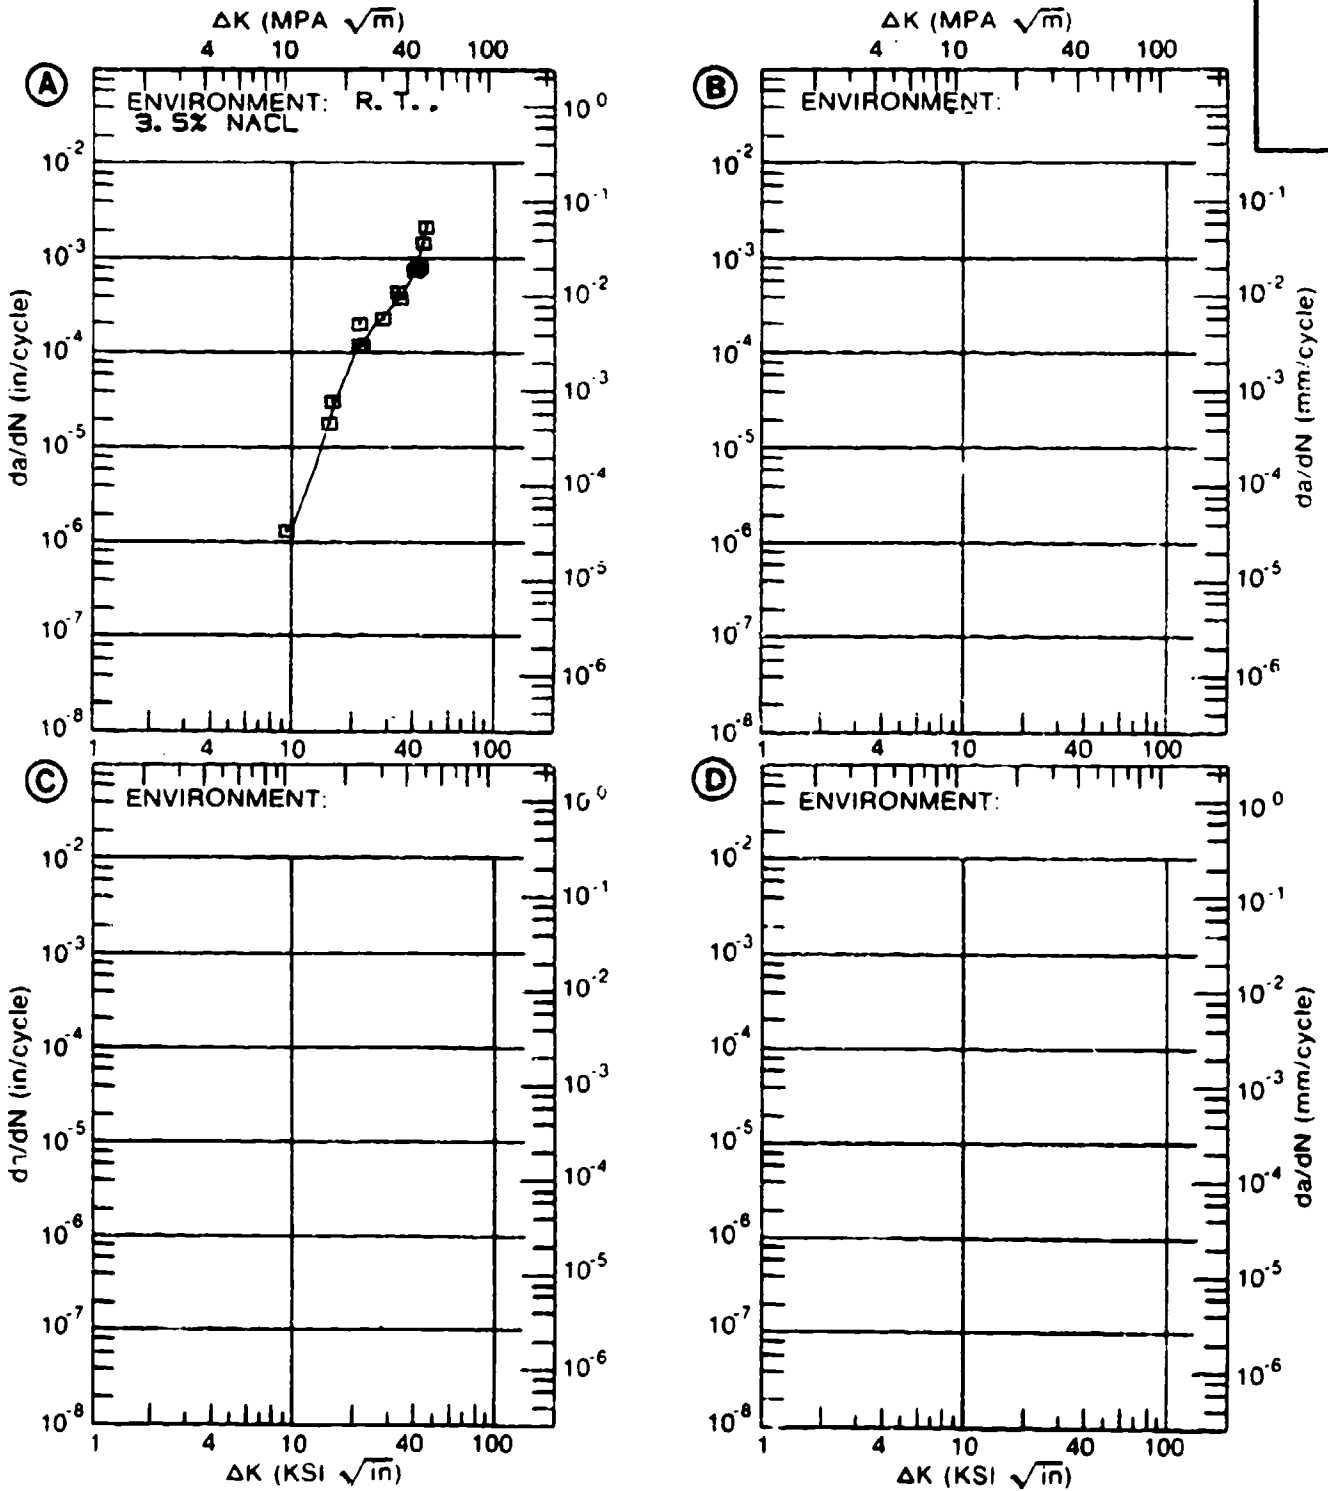


Figure 4.13.3.11

TABLE 4.13.3.12

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.12 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-6AL-6V-2SN			
CONDITION: STQA					
ENVIRONMENT: R. T. , HUMID AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K	A: 7.71	.61			
MIN	B: 4.54		.23		
	C:				
	D:				
	5.00		.334		
	6.00		.592		
	7.00		.907		
	8.00	.764	1.29		
	9.00	1.40	1.77		
	10.00	2.16	2.38		
	13.00	4.71	5.66		
	16.00	7.45	13.9		
	20.00	12.4	49.5		
	25.00	24.7			
	30.00	56.3			
	35.00	146.			
	40.00	421.			
DELTA K	A: 41.04	531.			
MAX	B: 22.27		105.		
	C:				
	D:				
ROOT MEAN SQUARE		16.17	19.45		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: STDA
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., HUMID AIR

YIELD STRENGTH: 180.3 KSI
 ULT. STRENGTH: 187.8 KSI
 SPECIMEN THK: 0.375"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90881

TITAN.
 ALLOY

TI-6AL-
 6V-2SN

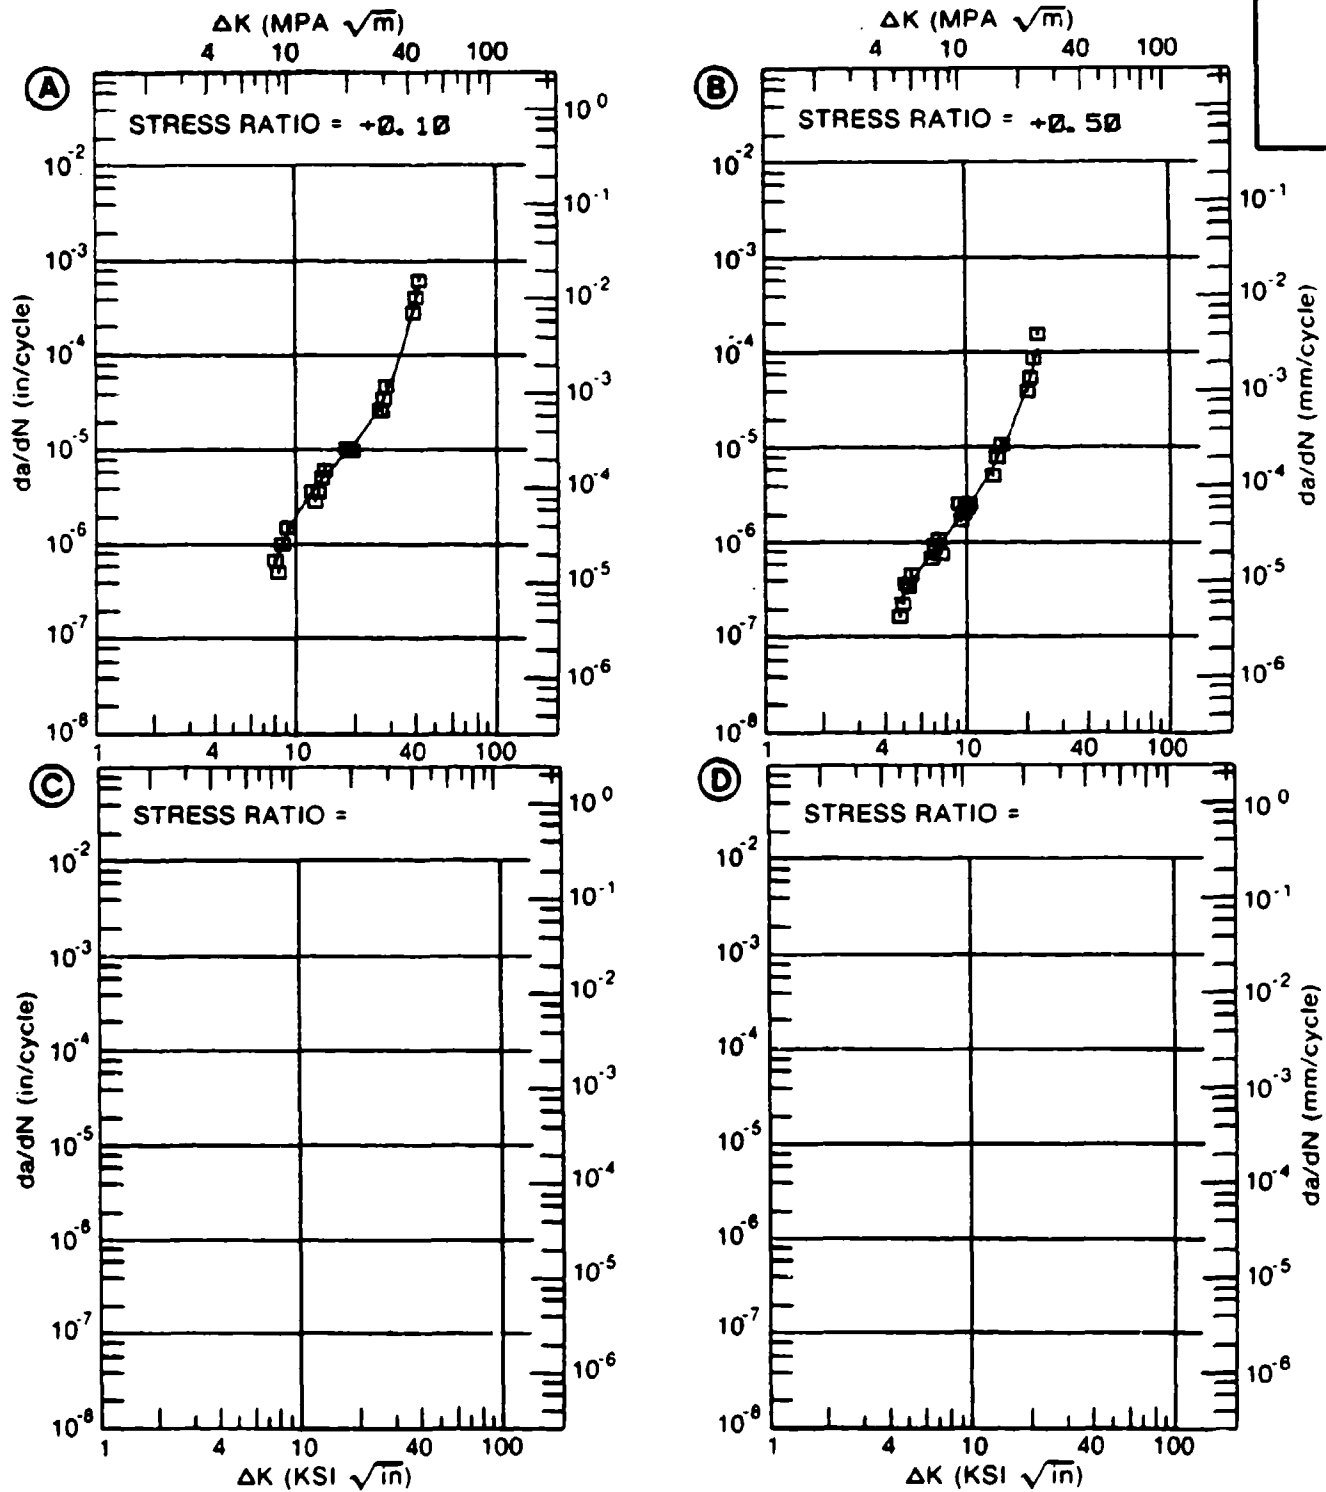


Figure 4.13.3.12

TABLE 4.13.3.13

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.13 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: STOA

TI-6AL-6V-2SN

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	E= R. T. 3. 5% NACL			
DELTA K A: 8. 30	1. 38			
MIN B:				
C:				
D:				
9. 00	1. 71			
10. 00	2. 35			
13. 00	6. 07			
16. 00	13. 5			
20. 00	30. 1			
DELTA K A: 23. 43	48. 2			
MAX B:				
C:				
D:				

ROOT MEAN SQUARE 15. 51
PERCENT ERROR

LIFE 0. 0-0. 5
PREDICTION 0. 5-0. 8
RATIO 0. 8-1. 25 1
SUMMARY 1. 25-2. 0
(NP/NA) >2. 0

CONDITION/HT: ST0A
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 0.10 HZ

YIELD STRENGTH: 180.3 KSI
 ULT. STRENGTH: 187.8 KSI
 SPECIMEN THK: 0.375"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 00001

TITAN.
 ALLOY

TI-6AL-
 6V-2SN

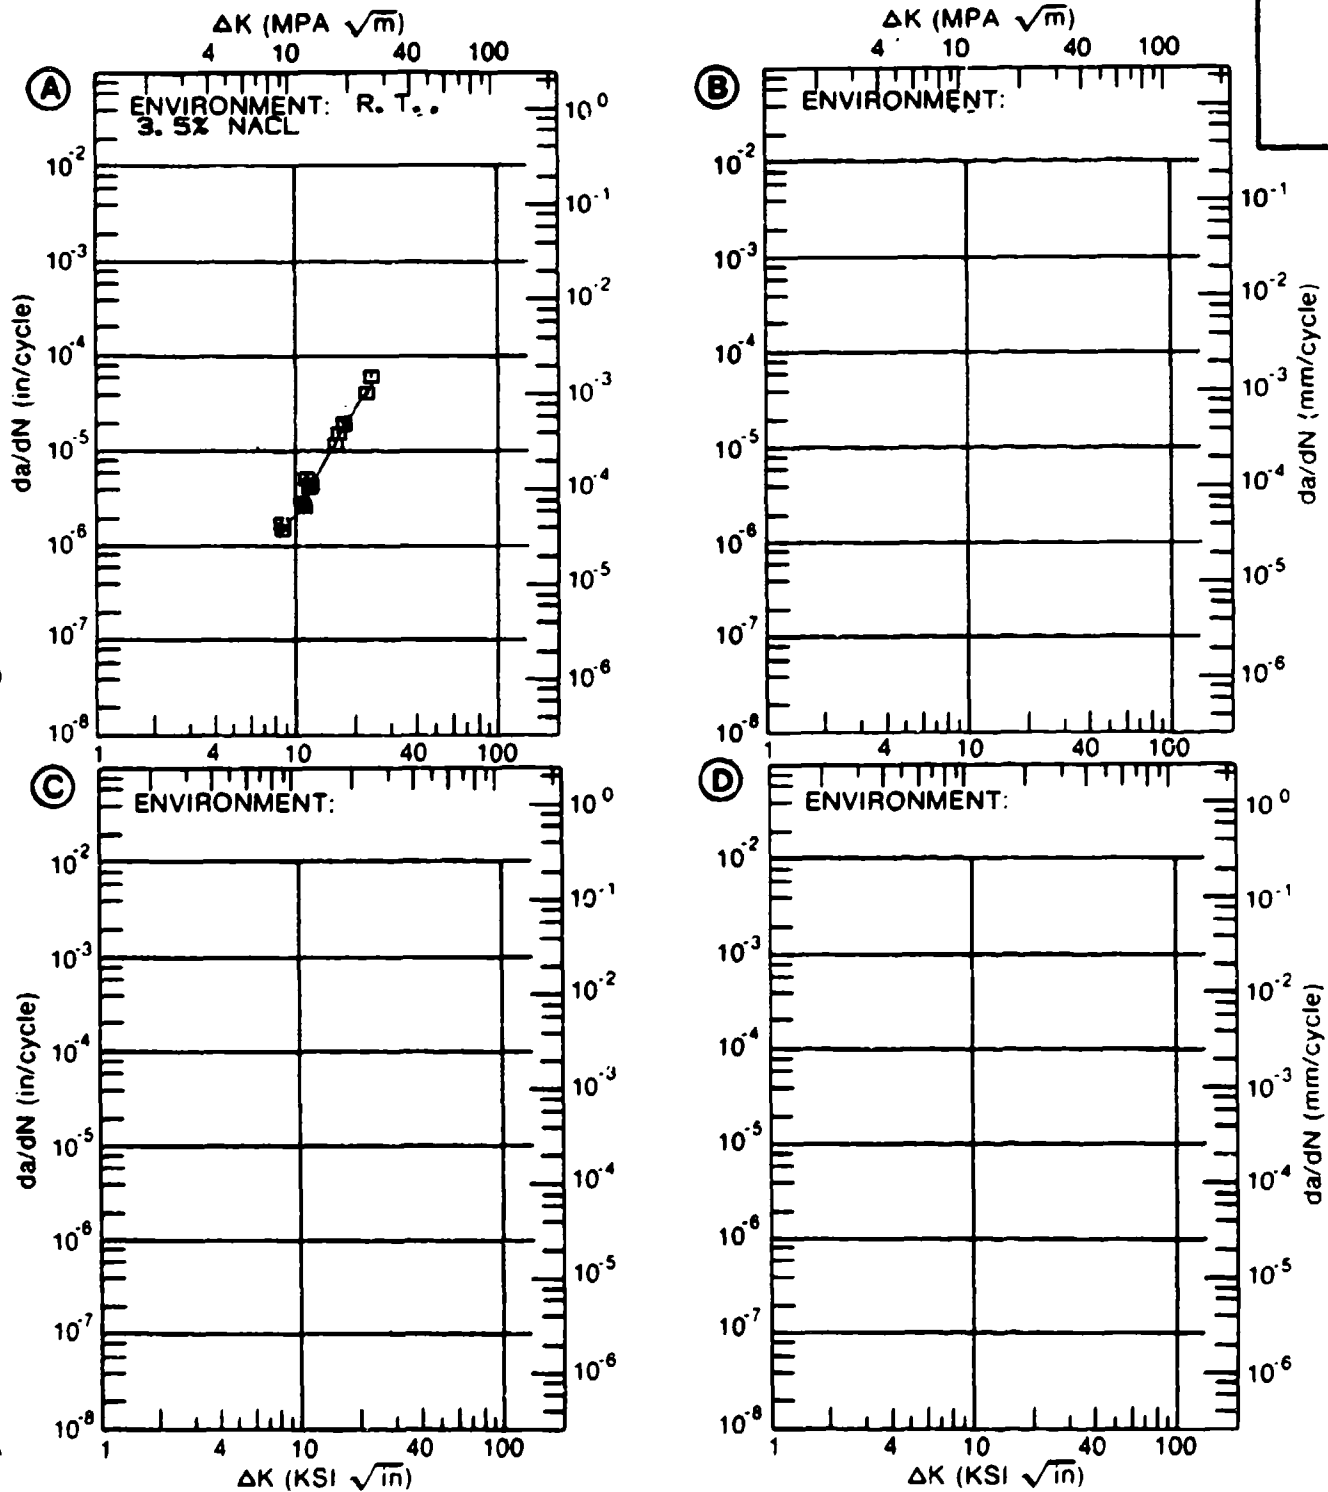


Figure 4.13.3.13

TABLE 4.13.3.14

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.13.3.14 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-6V-2SN			
CONDITION: STOA					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. H. H. A. 1HZ	E= R. T. 3. 5% NACL 1HZ	E= R. T. H. H. A. 20HZ	E= R. T. 3. 5% NACL 20HZ
DELTA K	A: 7.86	.602			
MIN	B: 6.57		.540		
	C: 4.47			.0681	
	D: 4.61				.174
	5.00			.118	.231
	6.00			.240	.469
	7.00		.634	.419	.869
	8.00	.652	1.01	.715	1.45
	9.00	1.08	1.60	1.17	2.21
	10.00	1.64	2.35	1.76	3.13
	13.00	4.12	5.51	4.20	6.72
	16.00	7.84	12.8	7.53	11.4
	20.00	15.1	38.4	13.4	19.3
	25.00	29.4	85.1	24.3	32.8
	30.00	52.4	150.	41.2	51.9
	35.00	89.5	264.	68.5	79.2
	40.00	149.	505.	113.	
	50.00	396.	2561.		
	60.00	1011.			
DELTA K	A: 63.06	1341.			
MAX	B: 54.97		6717.		
	C: 45.10			187.	
	D: 39.72				116.
ROOT MEAN SQUARE		14.47	19.12	9.46	12.48
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1	1	1

CONDITION/HT: ST0A
 FORM: Ø. 63" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +Ø. 1Ø
 FREQUENCY:

YIELD STRENGTH: 16Ø. Ø KSI
 ULT. STRENGTH: 17Ø. Ø KSI
 SPECIMEN THK: Ø. 14Ø- Ø. 151"
 SPECIMEN WIDTH: 3. ØØØ"
 REFERENCES:ØØØ44

TITAN.
 ALLOY
 TI-ØAL-
 6V-2SN

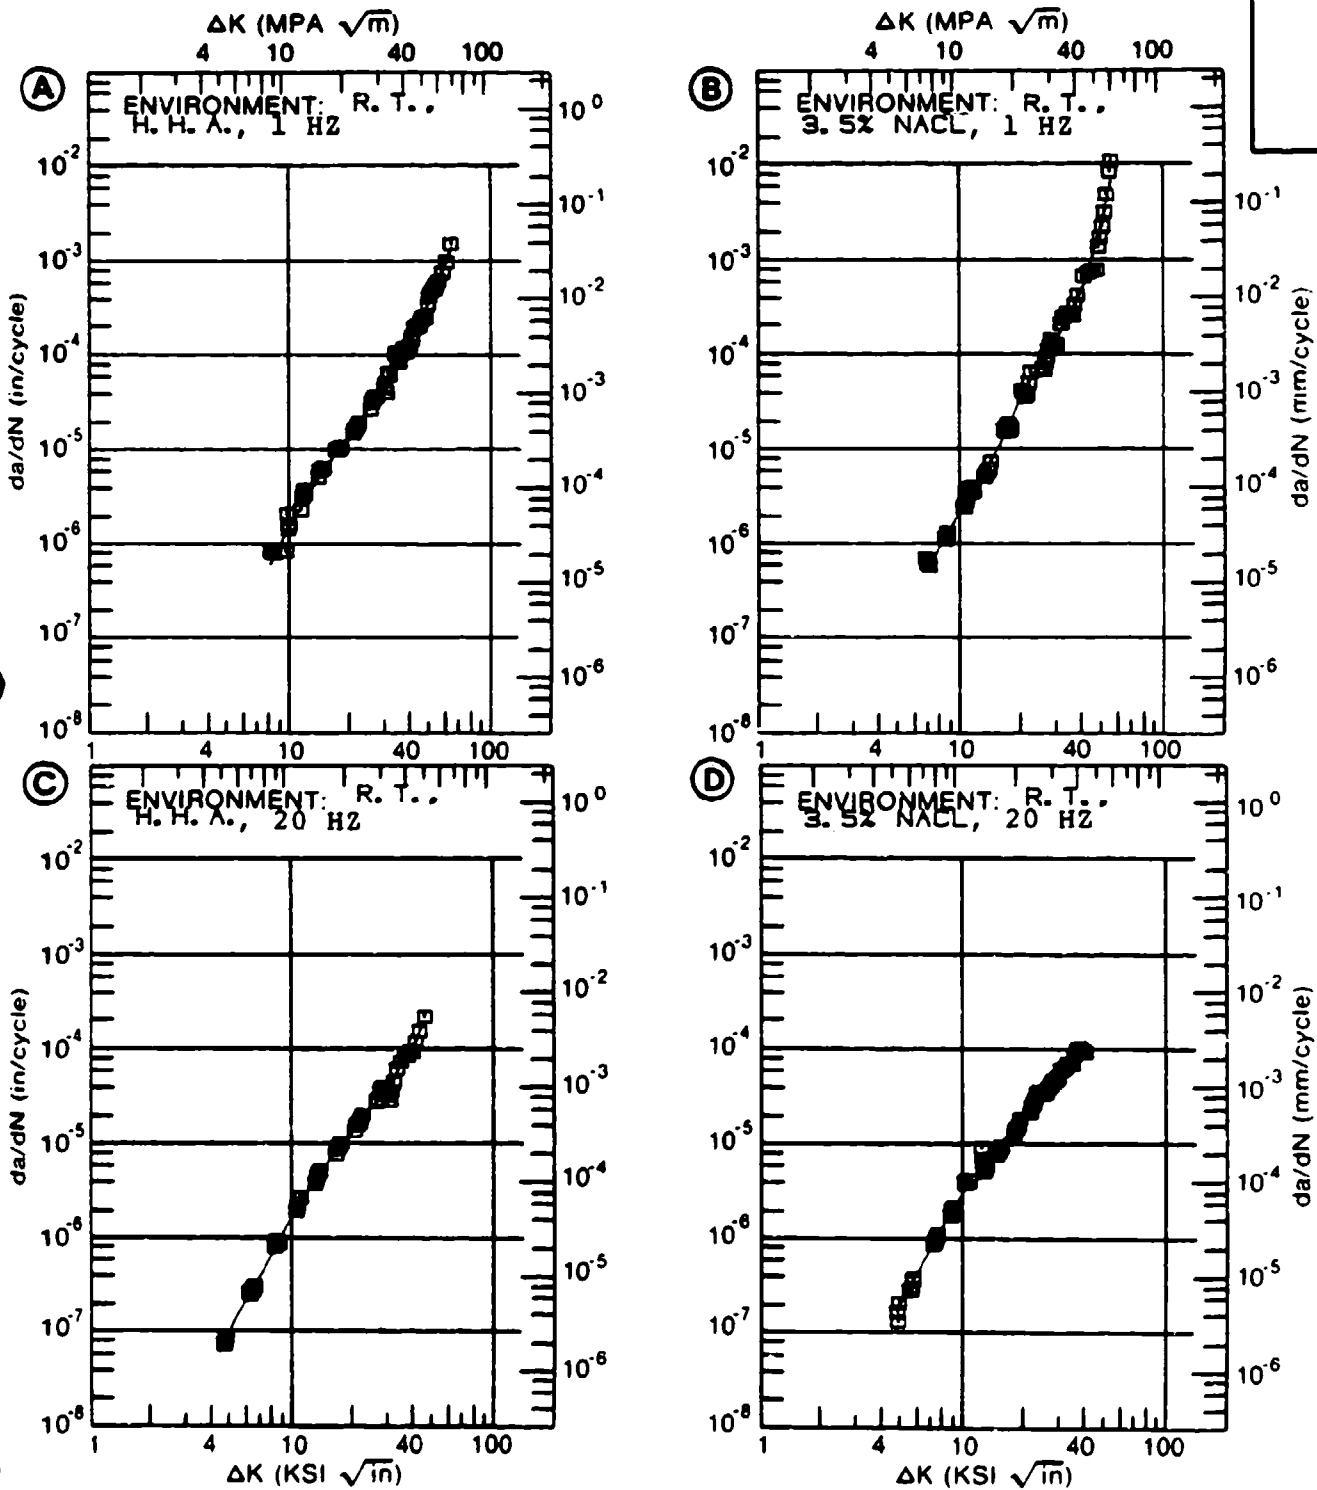


Figure 4.13.3.14

TABLE 4.13.3.15

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.13.3.15 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-6AL-6V-2SN			
CONDITION: 1300F 2HR					
K MAX (KSI*IN**1/2)		DA/DT (10**-3 IN/HOUR)			
		A	B	C	D
		E= R. T. 3.5% NACL	E= R. T. JP-4 FUEL		
K MAX	A:				
MIN	B:				
	C:				
	D:				
	200.00				
K MAX	A:				
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		0.00	0.00		
PERCENT ERROR					

CONDITION/HT: 1300F 2HR
 FORM: 2.0" TH FORGING
 SPECIMEN TYPE: TDCB
 ORIENTATION: L-T
 YIELD STRENGTH: 140.0 KSI
 ULT. STRENGTH:

SPECIMEN THK: 1.250"
 SPECIMEN WIDTH: 5.500"
 CRACK LENGTH (A₀):
 K_{ISCC}: 32.00 KSI (SQRT IN)
 REFERENCES: 84380

TITAN.
 ALLOY

TI-6AL-
 8V-2SN

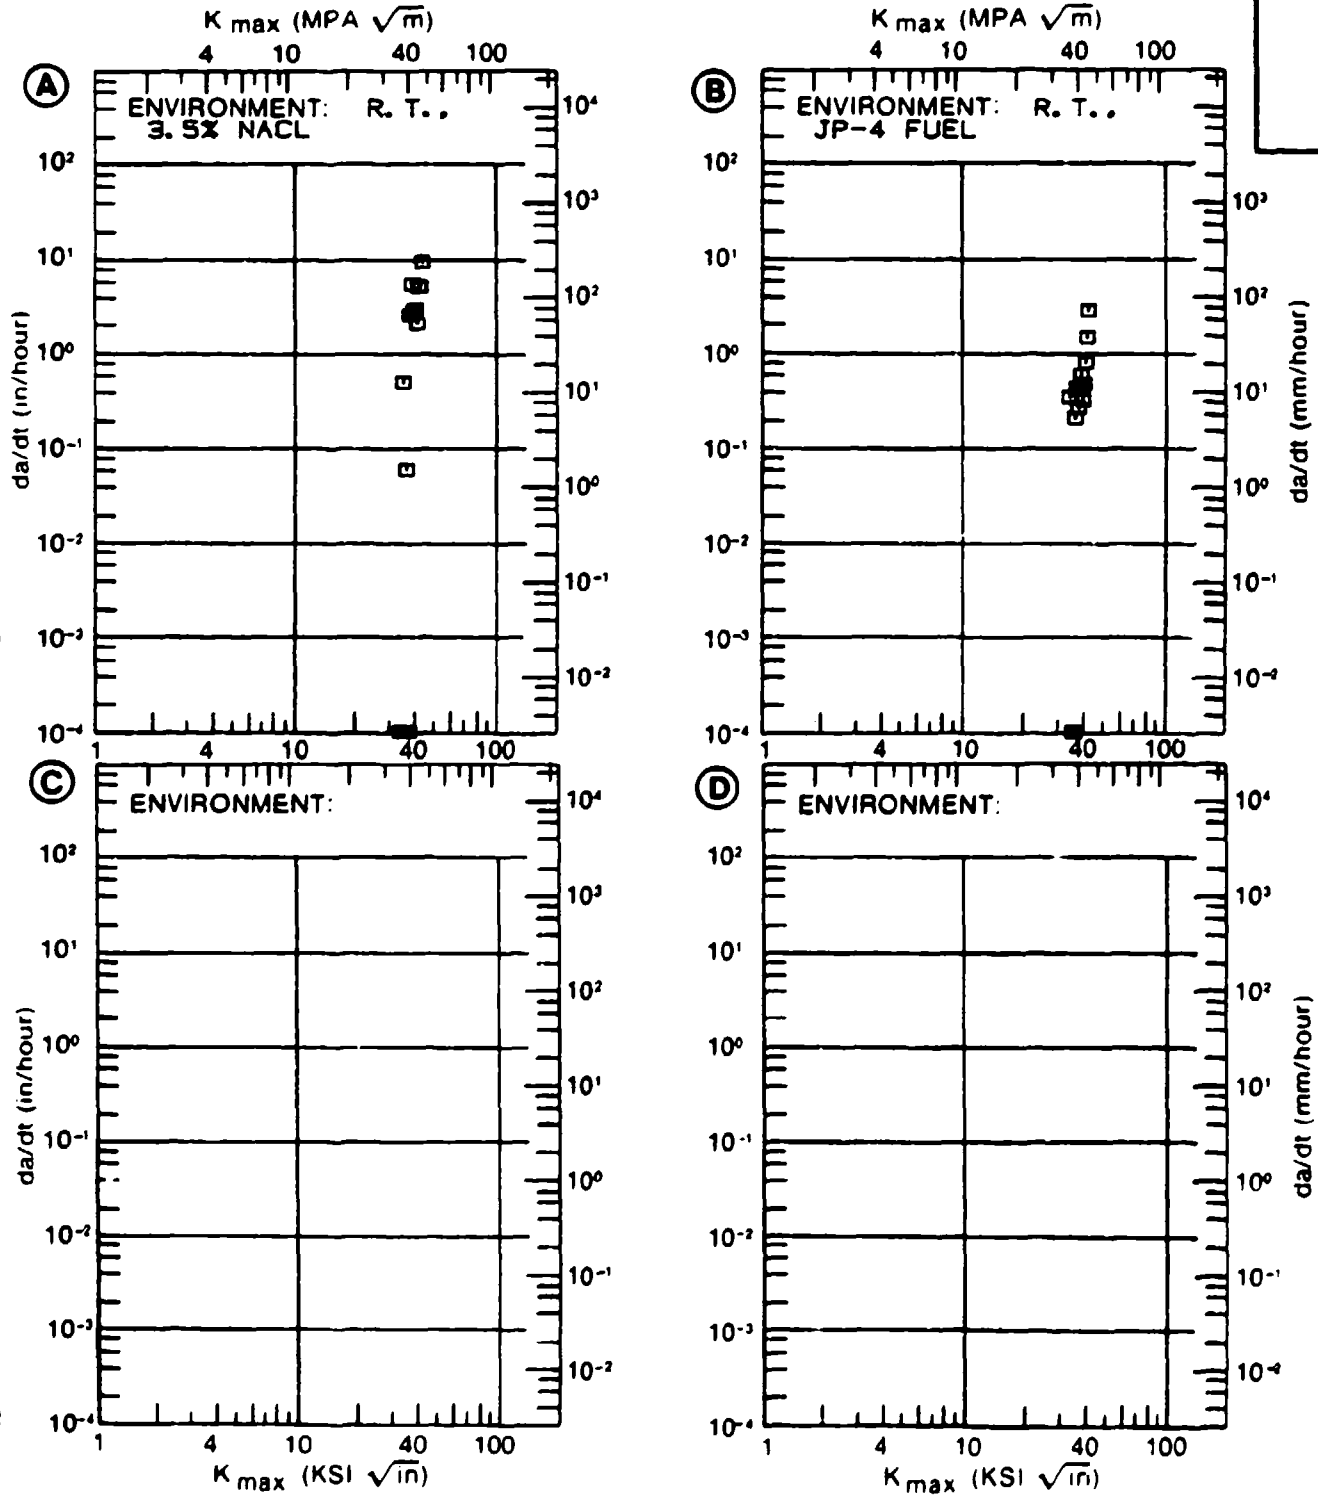


Figure 4.13.3.15

TABLE 4.14.3.1

TITANIUM		TI-6AL-6V-2.5SN K(ISSC)		SPECIMEN		CRACK		STAN		TEST				
CONDITION	PRODUCT FORM	THICK (IN)	TEMP (F)	TEST SPEC OR STR (RSI)	YIELD (RSI)	ENVIRONMENT	WIDTH (IN)	THICK (IN)	DESIGN (IN)	K(ISSC)	MEAN (RSI)	DEV	TIME (MIN)	DATE REFER
							W	B	A					
	P		R.T.		184.0	3.5 PCT NaCl			CANT	55.00	21.00			1967 70887
1050F 20R AC	F	2.20	R.T.	L-1	159.1	JF-4 FUEL	9.000	1.250	TDCB	57.10	30.50			1971 84360
1500F 20R AC	F	2.20	R.T.	L-1	146.2	3.5 PCT NaCl	9.000	1.250	TDCB	47.50	32.40			1971 84360
1550F 14R 40R AC	P	1.00	R.T.	T-5	179.6	3.5 PCT NaCl	1.000	0.750	CANT	55.00	21.00			1967 70931

TABLE 4.15.2.1

CONDITION	--PRODUCT--		TEST SPECIMEN		YIELD		STRENGTH		WIDTH		SECTION		LENGTH		CRACK (IN)	2.50 (IN)	R(1C) STAIN (R(1C) MEAN REV (SUBJECTIVE))	DATE	REFER
	FURN	(100) (T)	TEMP	ORIENT	(KSI)	(MPa)	(%)	(MPa)	(KSI)	(MPa)	(IN)	(IN)	(IN)	(IN)					
TITANIUM 71-6422827400 R(1C)																			
-----SPECIMEN-----																			
BETA FROSTED F	2 00	R T	---	---	154.6	---	---	---	2 000	---	---	---	---	---	---	0.52	71.44	----	81003
BETA FRO-100% F	2 75	R T	---	---	148.0	---	---	---	2 000	---	---	---	---	---	---	0.09	28.50	---	1974 80742 (1)
BETA FRO-50% F	2 75	R T	---	---	148.0	---	---	---	2 000	---	---	---	---	---	---	0.08	24.70	---	1974 80742 (1)
BETA FRO-25% F	2 75	R T	---	---	148.0	---	---	---	2 000	---	---	---	---	---	---	0.09	28.50	---	1974 80742 (1)
10% PRIMARY ALPHA, HELL, ANNEALED 1300F 1 HR, AC																			

BETA FRO-100% F	2 75	R T	---	---	142.0	---	---	---	2 000	---	---	---	---	---	---	0.10	31.40	---	1974 80742 (1)
BETA FRO-50% F	2 75	R T	---	---	142.0	---	---	---	2 000	---	---	---	---	---	---	0.09	30.40	---	1974 80742 (1)
BETA FRO-25% F	2 75	R T	---	---	142.0	---	---	---	2 000	---	---	---	---	---	---	0.10	31.30	---	1974 80742 (1)
10% PRIMARY ALPHA, SOLUTION TREATED & AGED 1425F 1 HR, AC, 1100F 0 HR, AC																			

BETA FRO-100% F	2 75	R T	---	---	148.0	---	---	---	2 000	---	---	---	---	---	---	0.08	27.10	---	1974 80742 (1)
BETA FRO-50% F	2 75	R T	---	---	148.0	---	---	---	2 000	---	---	---	---	---	---	0.10	29.70	---	1974 80742 (1)
BETA FRO-25% FRO-100% ALPHA, SOLUTION TREATED & AGED 1425F 1 HR, AC, 1300F 1 HR, AC																			

BETA FRO-100% F	2 75	R T	---	---	154.0	---	---	---	2 000	---	---	---	---	---	---	0.05	22.70	---	1974 80742 (1)
BETA FRO-50% F	2 75	R T	---	---	154.0	---	---	---	2 000	---	---	---	---	---	---	0.04	24.90	---	1974 80742 (1)
BETA FRO-25% FRO-50% PRIMARY ALPHA, HELL, ANNEALED 1300F 1 HR, AC																			

BETA FRO-100% F	2 75	R T	---	---	147.0	---	---	---	2 000	---	---	---	---	---	---	0.05	24.00	---	1974 80742 (1)
BETA FRO-50% F	2 75	R T	---	---	147.0	---	---	---	2 000	---	---	---	---	---	---	0.05	24.00	---	1974 80742 (1)
BETA FRO-25% FRO-50% PRIMARY ALPHA, SOLUTION TREATED & AGED 1425F 1 HR, AC, 1100F 0 HR, AC																			

BETA FRO-100% F	2 75	R T	---	---	159.0	---	---	---	2 000	---	---	---	---	---	---	0.14	40.50	---	1974 80742 (1)
BETA FRO-50% F	2 75	R T	---	---	159.0	---	---	---	2 000	---	---	---	---	---	---	0.10	42.50	---	1974 80742 (1)
BETA FRO-25% FRO-50% PRIMARY ALPHA, SOLUTION TREATED & AGED 1425F 1 HR, AC, 1100F 0 HR, AC																			

NOTES
1. 1) COMP DATA

TABLE 4.15.2.1 (con't)

CONDITION	FURN		TEMP		YIELD STRENGTH (KSI)		TENSILE STRENGTH (KSI)		REDUCTION OF AREA (%)		ELONGATION IN GAUGE LENGTH (IN)		CRACK LENGTH (IN)		R(1C) STAIN DEPTH (MIL)		DATE	REFER	
	NO.	TYPE	2.75	R.T.	157.0	2.000	1.000	CT	1.000	0.17	41.30	0.9	1974	89762	(1)				
ALPHA-BETA F	2.75	R.T.	141.0	2.000	1.000	CT	1.000	0.13	36.90										
BETA F	2.75	R.T.	141.0	2.000	1.000	CT	1.000	0.15	38.90										
ALPHA-BETA F TM	2.75	R.T.	141.0	2.000	1.000	CT	1.000	0.13	36.40										
SOLVED 50% REDUCTION SOLUTION TREATED & AGED 1625F 1 HR. 1100F 8 HR. AC																			
ALPHA-BETA F	2.75	R.T.	153.0	2.000	1.000	CT	1.000	0.22	43.80										
BETA F	2.75	R.T.	153.0	2.000	1.000	CT	1.000	0.20	43.40										
ALPHA-BETA F	2.75	R.T.	153.0	2.000	1.000	CT	1.000	0.21	44.80										
SOLVED 10% REDUCTION SOLUTION TREATED & AGED 1625F 1 HR. AC. 1100F 8 HR. AC																			
ALPHA-BETA F	2.75	R.T.	143.0	2.000	1.000	CT	1.000	0.10	32.40										
BETA F	2.75	R.T.	143.0	2.000	1.000	CT	1.000	0.10	32.70										
ALPHA-BETA F	2.75	R.T.	143.0	2.000	1.000	CT	1.000	0.09	31.60										
ALPHA-BETA F	2.75	R.T.	144.0	2.000	1.000	CT	1.000	0.08	29.20										
BETA F	2.75	R.T.	144.0	2.000	1.000	CT	1.000	0.08	30.20										
ALPHA-BETA F	2.75	R.T.	144.0	2.000	1.000	CT	1.000	0.09	31.20										
SOLVED 10% REDUCTION SOLUTION TREATED & AGED 1625F 1 HR. AC. 1100F 8 HR. AC																			
ALPHA-BETA F	2.00	R.T.	150.0	2.000	2.000	---	---	0.21	43.94										

NOTES
 (1) CRF DISK
 (2) CRF DISK COMPOSE GRAIN SIZE
 (3) CRF DISK FINE GRAIN SIZE

TABLE 4.16.1.1
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 TITANIUM TI-8AL-1ND-1V

TEST CONDITIONS		ENVIRONMENT		FATIGUE CRACK GROWTH RATES						
SPECIMEN ORIENTATION	L-T	LAB AIR	AT R.T.	DELTA K LEVELS: (KSI SQRT(IN))	2.5	5	10	20	50	100
CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	FATIGUE CRACK GROWTH RATES (MICR IN/CYCLE)						
	SHEET	0.02	0 10-12 00		2.28	13.5	144			1243
DA	SHEET	0.00	1 00-30 00						67.2	
DA	SHEET	0.10	43.00				7.56	246		
DA	SHEET	0.25	1 00-30 00						162	
DA	SHEET	0.43	1 00-30.00				13.3			
DA	SHEET	0.67	1 00-30 00		2.22					
MA	SHEET	0.10	43.00						7.47	

TABLE 4.16.2.1

CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	TI-6AL-4V K(IIC)		CRACK LENGTH (IN)	2.96 K(IIC)/TYS)**2 (IN)	K(IIC) MEAN (K(IIC) SORT IN)	STAH DEV	DATE	REFER
						WIDTH (IN)	THICK (IN)						
PROOF THR 40, 1100F RHNS AC	F	---	R T	C-R	142.0	W	0.500	---	0.18	38.32		1977 PH002	
						B	0.500	---					
						A							

TABLE 4.16.2.2

TITANIUM		TI-BAL-1MO-IV K(IC)										K(IC) STAN				
CONDITION	FORM	THICK (IN)	TEMP (F)	SPEC YIELD (KSI)	SPECIMEN		CRACK LENGTH CROSS STRESS				K(APP) MEAN DEV (KSI*SQRT IN)	K(C) MEAN DEV (KSI*SQRT IN)	STAN	DATE	REFER	
					WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)						K(APP) (KSI*SQRT IN)
DA	S	0.02	R.T.	L-T	135.5	9.000	0.020	2.110	2.630	62.20	73.30	138.16	157.35			1966 67821
DA	S	0.02	R.T.	L-T	135.5	12.000	0.020	0.560	0.700	79.00	110.20	105.54*	115.80*			1966 67821
		0.02			135.5	12.000	0.020	2.120	2.800	42.50	55.90	104.02	121.33			1966 67821
		0.02			135.5	12.000	0.020	2.020	2.360	41.60	47.90	86.85	94.49			1966 67821
		0.02			135.5	12.000	0.020	0.950	1.240	75.00	85.00	104.24	98.4/10.0	111.7/15.0		1966 67821
DA	S	0.04	R.T.	L-T	132.6	9.000	0.045	2.100	2.970	45.90	66.10	124.25	153.19			1966 67821
DA	S	0.05	R.T.	L-T	133.6	8.000	0.050	1.500	3.050	62.00	87.50	137.30*	210.73*			1968 71709
		0.05			133.6	8.000	0.050	3.500	4.790	27.00	79.90	213.08*	285.48*			1968 71709
		0.05			133.6	8.000	0.050	1.020	2.100	75.20	105.00	134.26*	199.24*			1968 71709
		0.05			133.6	8.000	0.050	1.970	3.390	52.90	79.20	145.62	206.08*			1968 71709
		0.05			133.6	8.000	0.050	5.010	5.700	19.00	33.70	127.02	136.3/13.2	152.64*		1968 71709
DA	S	0.05	R.T.	L-T	133.6	20.000	0.050	2.060	9.000	62.40	85.90	155.54	250.46*			1968 71709
		0.05			133.6	20.000	0.050	2.020	4.000	29.10	77.40	138.75	198.94			1968 71709
		0.05			133.6	20.000	0.050	8.020	14.500	26.50	42.70	168.60	314.95*			1968 71709
		0.05			133.6	20.000	0.050	9.940	15.000	22.80	36.40	170.65	285.62*			1968 71709
		0.05			133.6	20.000	0.050	6.040	10.000	26.80	47.60	155.45	224.35			1968 71709
		0.05			133.6	20.000	0.050	9.980	15.600	19.30	30.50	143.50	259.41*			1968 71709
		0.05			133.6	20.000	0.050	4.800	11.080	36.40	45.60	160.64	236.94			1968 71709
		0.05			133.6	20.000	0.050	4.260	7.500	36.90	58.90	156.77	221.71			1968 71709
		0.05			133.6	20.000	0.050	3.760	7.520	48.60	67.80	173.43	198.1/11.8	263.23*	220.5/15.8	1968 71709
DA	S	0.05	R.T.	T-L	135.3	8.000	0.050	4.910	9.700	26.90	37.80	139.02	171.22*			1968 71709
		0.05			135.3	8.000	0.050	1.000	2.250	65.00	103.00	132.88*	207.62*			1968 71709
		0.05			135.3	8.000	0.050	2.940	4.250	39.40	62.00	145.55	195.48*			1968 71709
		0.05			135.3	8.000	0.050	2.020	3.450	42.90	80.10	148.56	220.88*			1968 71709
		0.05			135.3	8.000	0.050	1.320	3.100	51.70	91.80	145.09*	144.4/ 4.9	223.65*		1968 71709

*NOTE- NET SECTION STRESS EXCEEDS BOX OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 4.16.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-8AL-1MO-1V			
CONDITION:					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KBI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.02			
DELTA K	A: 6.38	.621			
MIN	B:				
	C:				
	D:				
	7.00	.824			
	8.00	1.22			
	9.00	1.70			
	10.00	2.28			
	13.00	4.56			
	16.00	7.75			
	20.00	13.5			
	25.00	23.6			
	30.00	37.3			
	35.00	55.4			
	40.00	78.7			
	50.00	144.			
	60.00	243.			
	70.00	387.			
	80.00	589.			
	90.00	867.			
	100.00	1243.			
DELTA K	A: 118.36	2281.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		34.16			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT:
 FORM: 0.05" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 0.10- 12.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 119.5 KSI
 ULT. STRENGTH: 134.0 KSI
 SPECIMEN THK: 0.050"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: MA011

TITAN.
 ALLOY

TI-6AL-
 1MO-1V

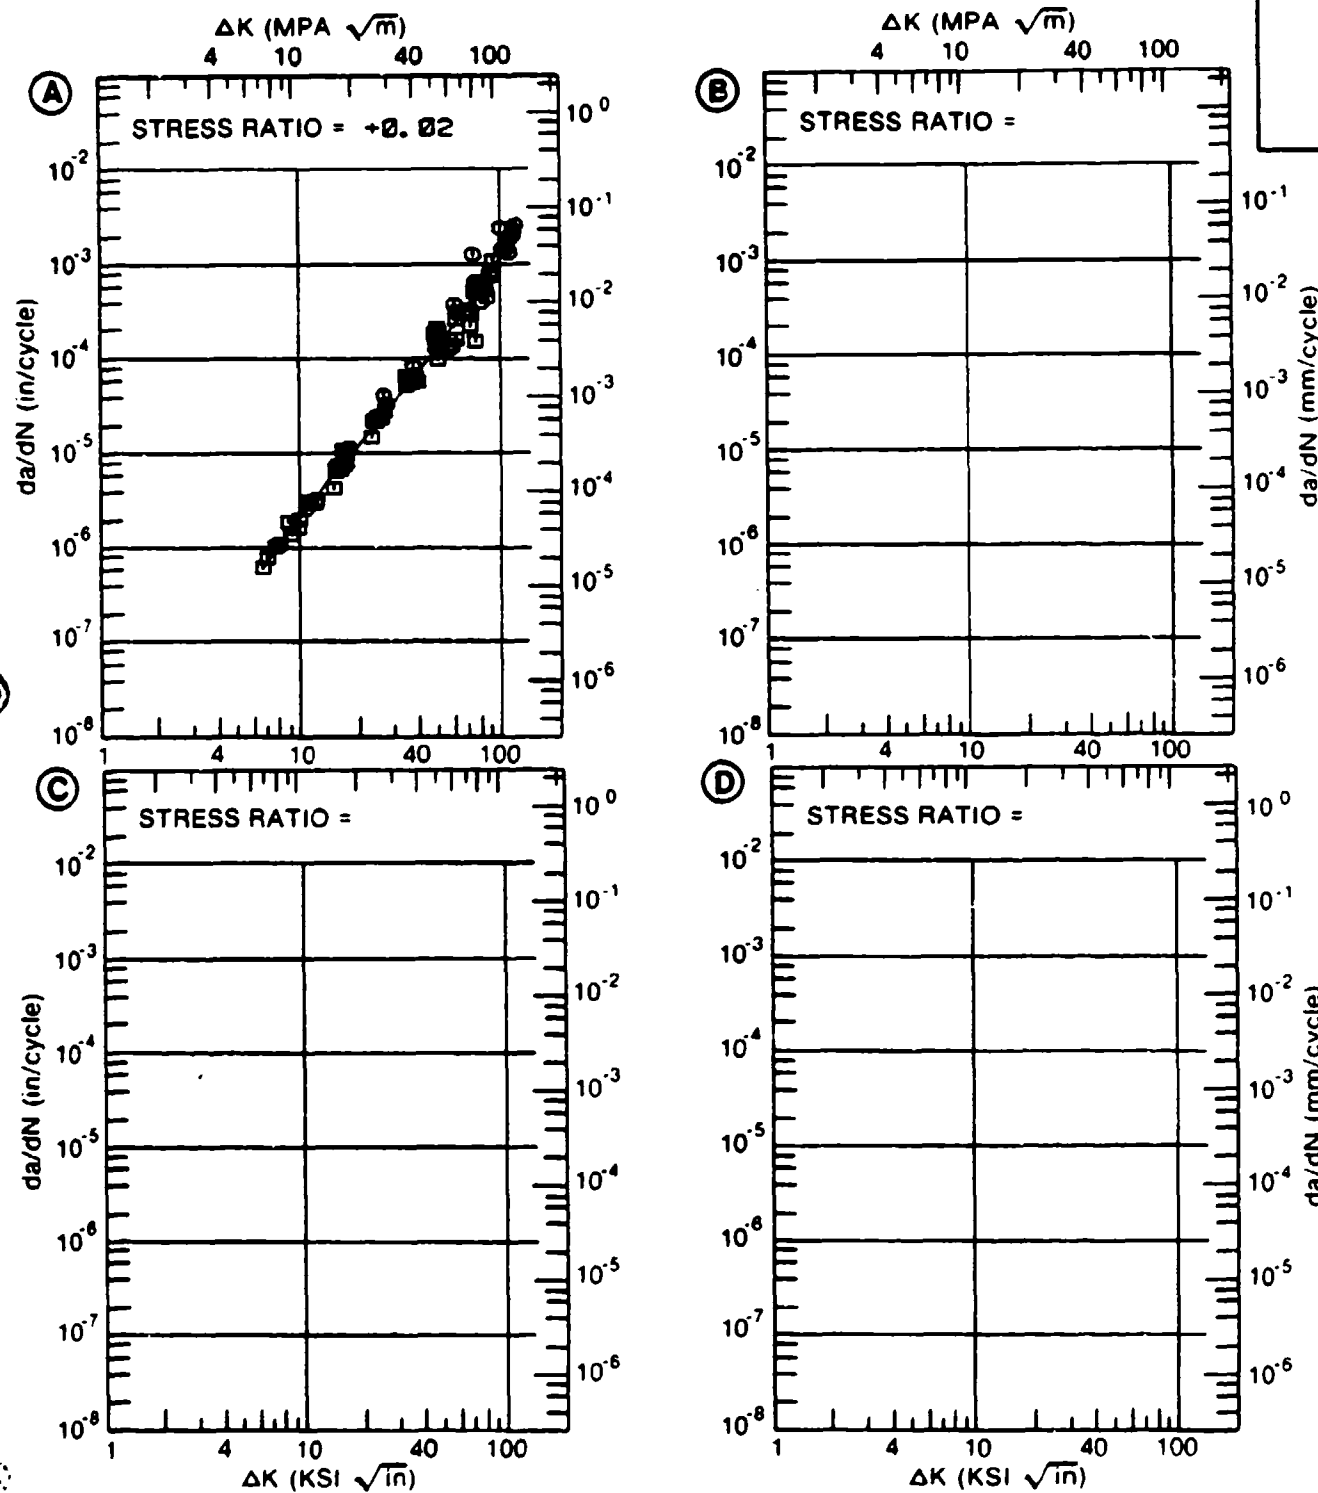


Figure 4.16.3.1

TABLE 4.16.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.2 INDICATING EFFECT
OF STRESS RATIO

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A: 17.97	5.41			
	B:				
	C:				
	D:				
	20.00	7.58			
	25.00	10.5			
	30.00	14.1			
	35.00	24.9			
	40.00	60.4			
	50.00	246.			
	60.00	787.			
DELTA K MAX	A: 62.14	1256.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		12.44			
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5	0.5-0.8	0.8-1.25	1.25-2.0	>2.0
			2		

CONDITION/HT: DA
 FORM: 0.05" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 43.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 140.0 KSI
 ULT. STRENGTH: 149.2 KSI
 SPECIMEN THK: 0.064"
 SPECIMEN WIDTH: 3.000"
 REFERENCES 96099

TITAN.
 ALLOY
 TI-8AL-
 1MO-1V

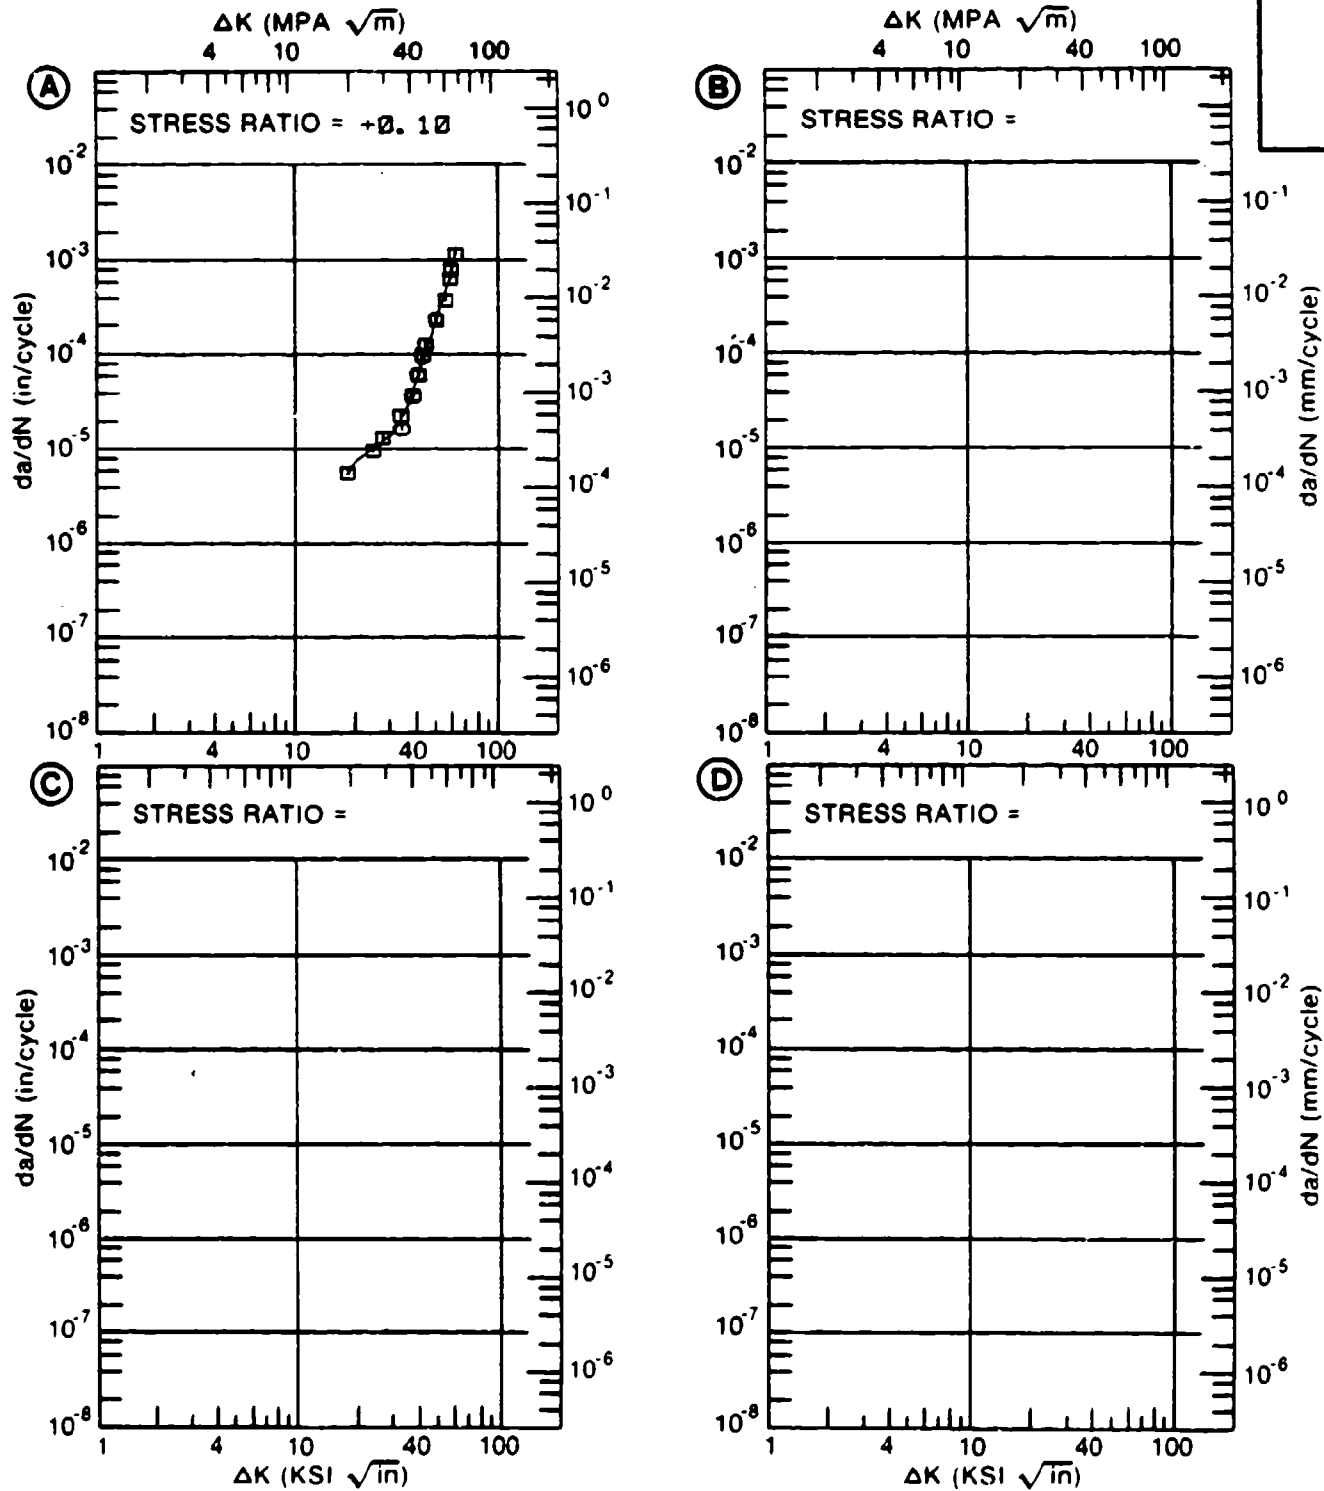


Figure 4.16.3.2

TABLE 4.16.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.3 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM		TI-BAL-1MD-1V			
CONDITION: DA					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.00	R=+0.25	R=+0.43	R=+0.67
DELTA K	A:				
MIN	B:	29.33	33.3		
	C:				
	D:				
		30.00	35.3		
		35.00	51.0		
		40.00	71.5		
		50.00	162.		
DELTA K	A:				
MAX	B:	59.13	439.		
	C:				
	D:				
ROOT MEAN SQUARE		0.00	6.87	0.00	0.00
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25		1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: DA
 FORM: 0.05" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00-30.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 136.3 KSI
 ULT. STRENGTH: 150.7 KSI
 SPECIMEN THK: 0.050"
 SPECIMEN WIDTH: 20.000"
 REFERENCES 86099

TITAN.
 ALLOY
 TI-6AL-
 4V

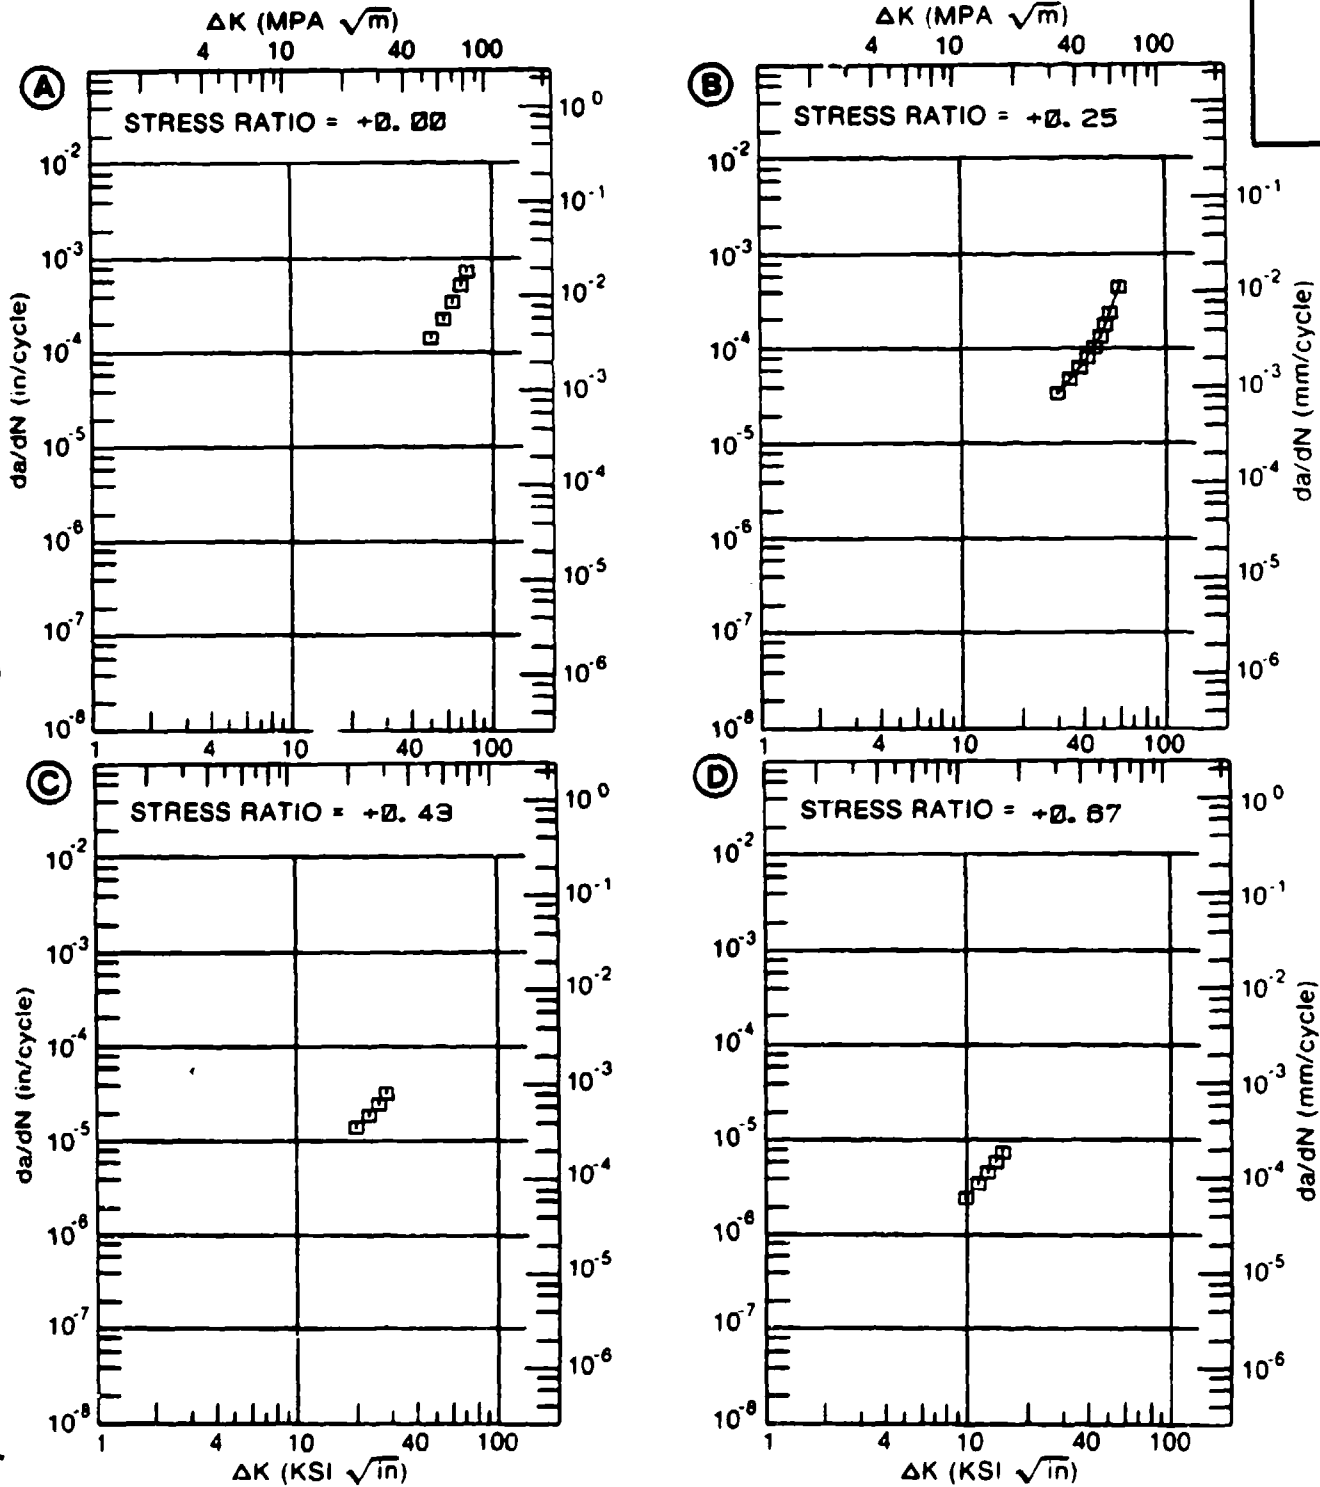


Figure 4.16.3.3

TABLE 4.16.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.4 INDICATING EFFECT

OF STRESS RATIO

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.00	R=+0.25	R=+0.43	R=+0.67
MATERIAL:	TITANIUM				
CONDITION:	DA				
ENVIRONMENT:	R.T. , LAB AIR				
	A: 37.15	28.2			
DELTA K MIN	B: 22.28		13.3		
	C: 14.82			6.14	
	D: 7.48				.598
	8.00				.860
	9.00				1.48
	10.00				2.22
	13.00				5.13
	16.00			7.88	10.2
	20.00			13.3	
	25.00		15.6	21.1	
	30.00		24.6		
	35.00		39.8		
	40.00	32.8	60.8		
	50.00	67.2			
DELTA K MAX	A: 56.83	95.6			
	B: 41.40		67.5		
	C: 28.99			32.5	
	D: 18.26				17.6
ROOT MEAN SQUARE PERCENT ERROR		16.65	12.77	9.57	19.18
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25	3	4	4	3
	1.25-2.0	1			1
	>2.0				

CONDITION/HT: DA
 FORM: 0.05" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00- 30.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 133.7- 136.3 KSI
 ULT. STRENGTH: 150.7- 152.1 KSI
 SPECIMEN THK: 0.050"
 SPECIMEN WIDTH: 2.000- 7.992"
 REFERENCES 98099

TITAN.
 ALLOY

TI-6AL-
 1MO-1V

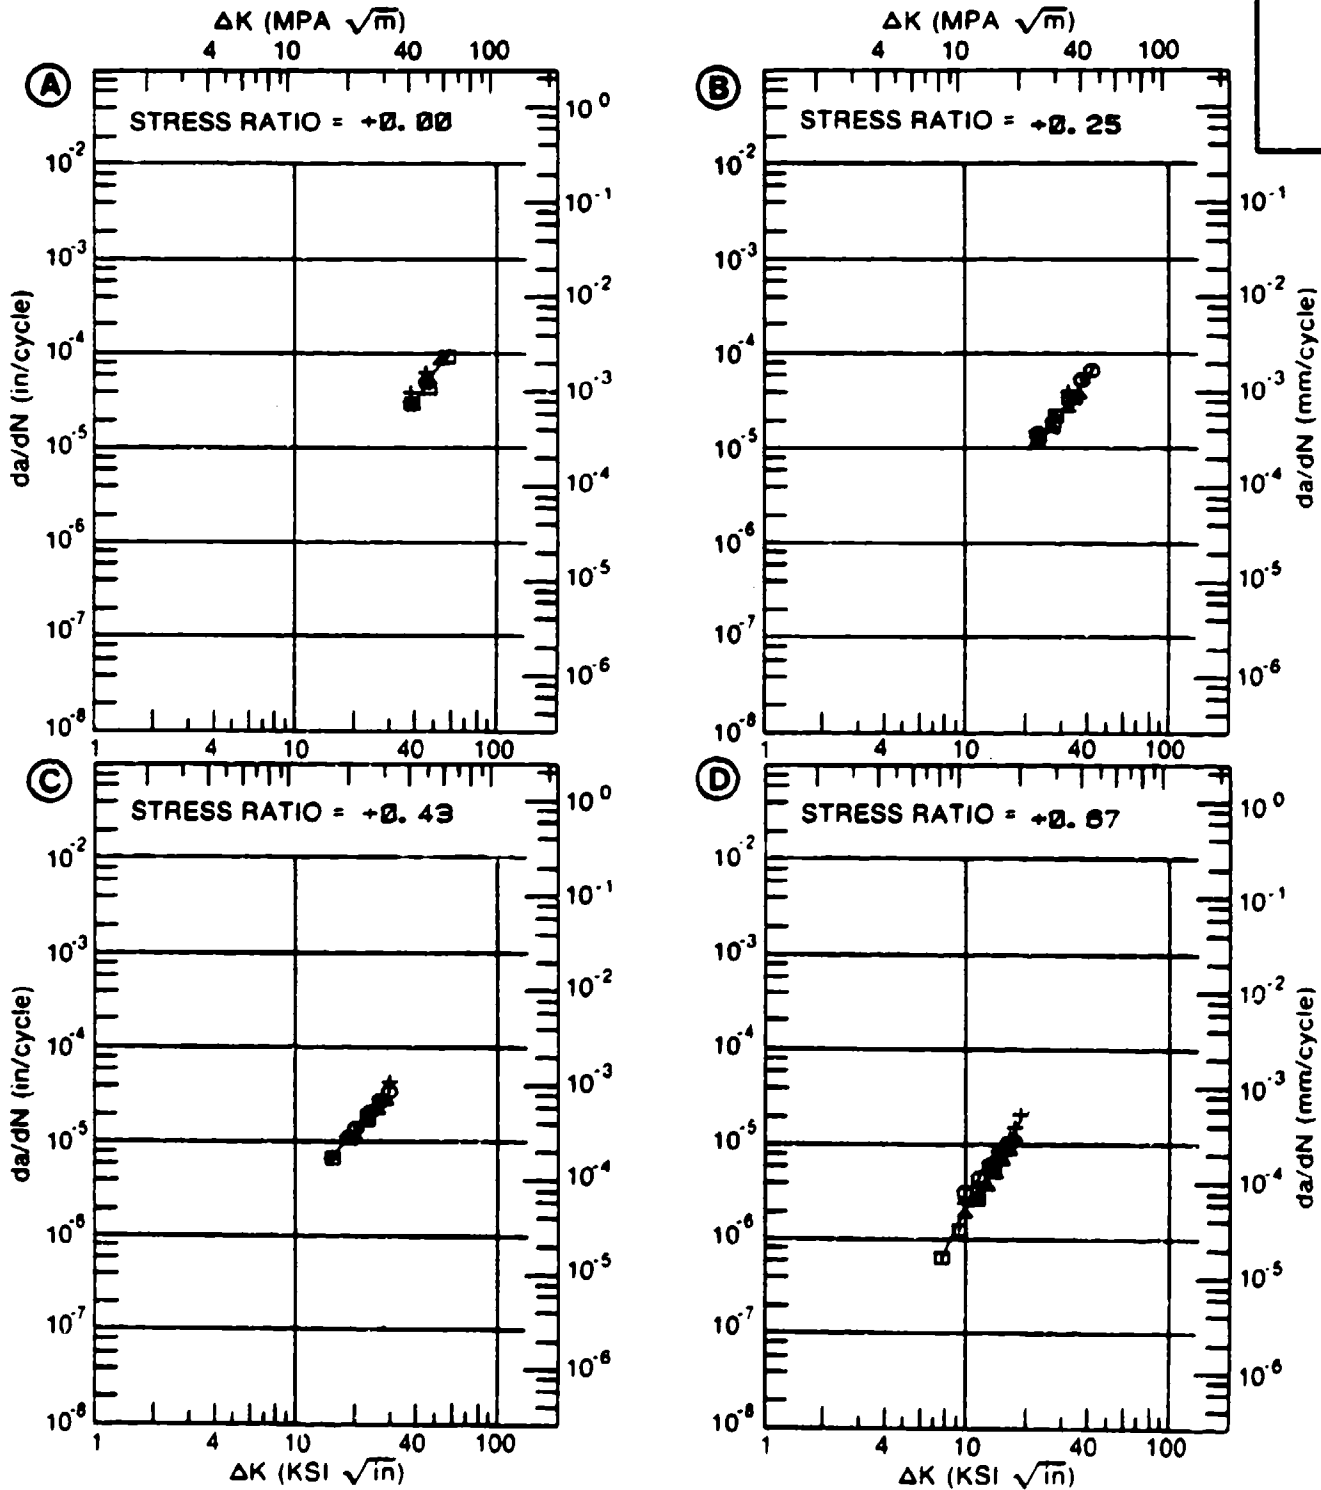


Figure 4.16.3.4

TABLE 4.16.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.5 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-BAL-1MO-1V
CONDITION: MA
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K	A: 19.10	6.63			
MIN	B:				
	C:				
	D:				
	20.00	7.47			
	25.00	10.2			
	30.00	24.4			
	35.00	54.3			
DELTA K	A: 39.05	87.0			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 28.77
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8 1
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: MA
 FORM: 8.82" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 42.88 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 154.9 KSI
 ULT. STRENGTH: 189.2 KSI
 SPECIMEN THK: 8.818"
 SPECIMEN WIDTH: 2.888"
 REFERENCES: 80809

TITAN.
 ALLOY
 TI-6AL-
 4V

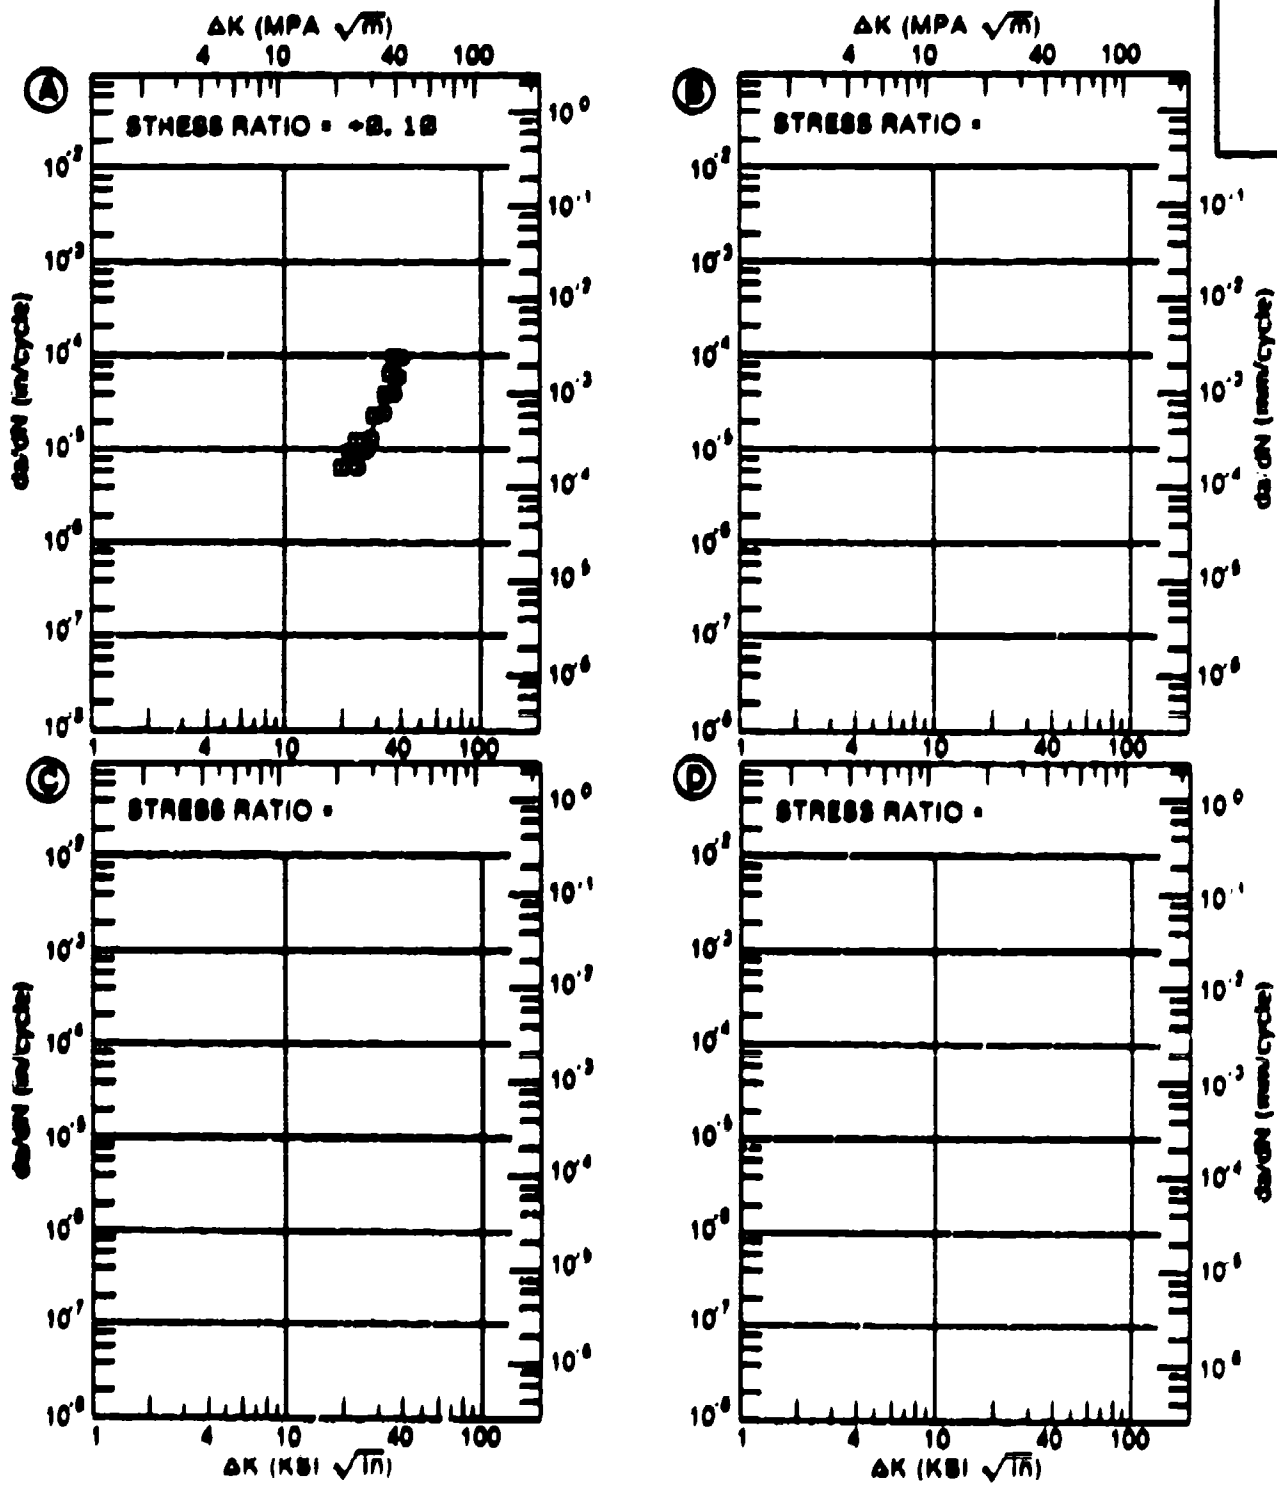


Figure 4.16.1.1

TABLE 4.16.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.6 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: TITANIUM TI-BAL-1MO-1V
CONDITION: 1625F 1HR AC, 1350F 2HRS AC
ENVIRONMENT: R.T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.00	R=+0.04	R=+0.54	
DELTA K MIN	A:	13.50	2.16		
	B:	6.37		.0417	
	C:	10.39			2.48
	D:				
		7.00		.0911	
		8.00		.214	
	9.00		.379		
	10.00		.581		
	13.00		1.60	6.62	
	16.00	2.86	4.92	19.0	
	20.00	10.6			
	25.00	23.3			
	30.00	75.2			
DELTA K MAX	A:	31.31	107.		
	B:	19.64		28.6	
	C:	16.74			21.9
	D:				
ROOT MEAN SQUARE		17.10	20.60	11.15	
PERCENT ERROR					

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1925F 1HR AC, 1350F 2HRS AC
 FORM: 2.50" TH FAN BLADES
 SPECIMEN TYPE: KB BAR
 ORIENTATION: L-T
 FREQUENCY: 0.33 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 120.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.251- 0.253"
 SPECIMEN WIDTH: 0.750"
 REFERENCES: GE006

TITAN.
 ALLOY

TI-8AL-
 1MO-1V

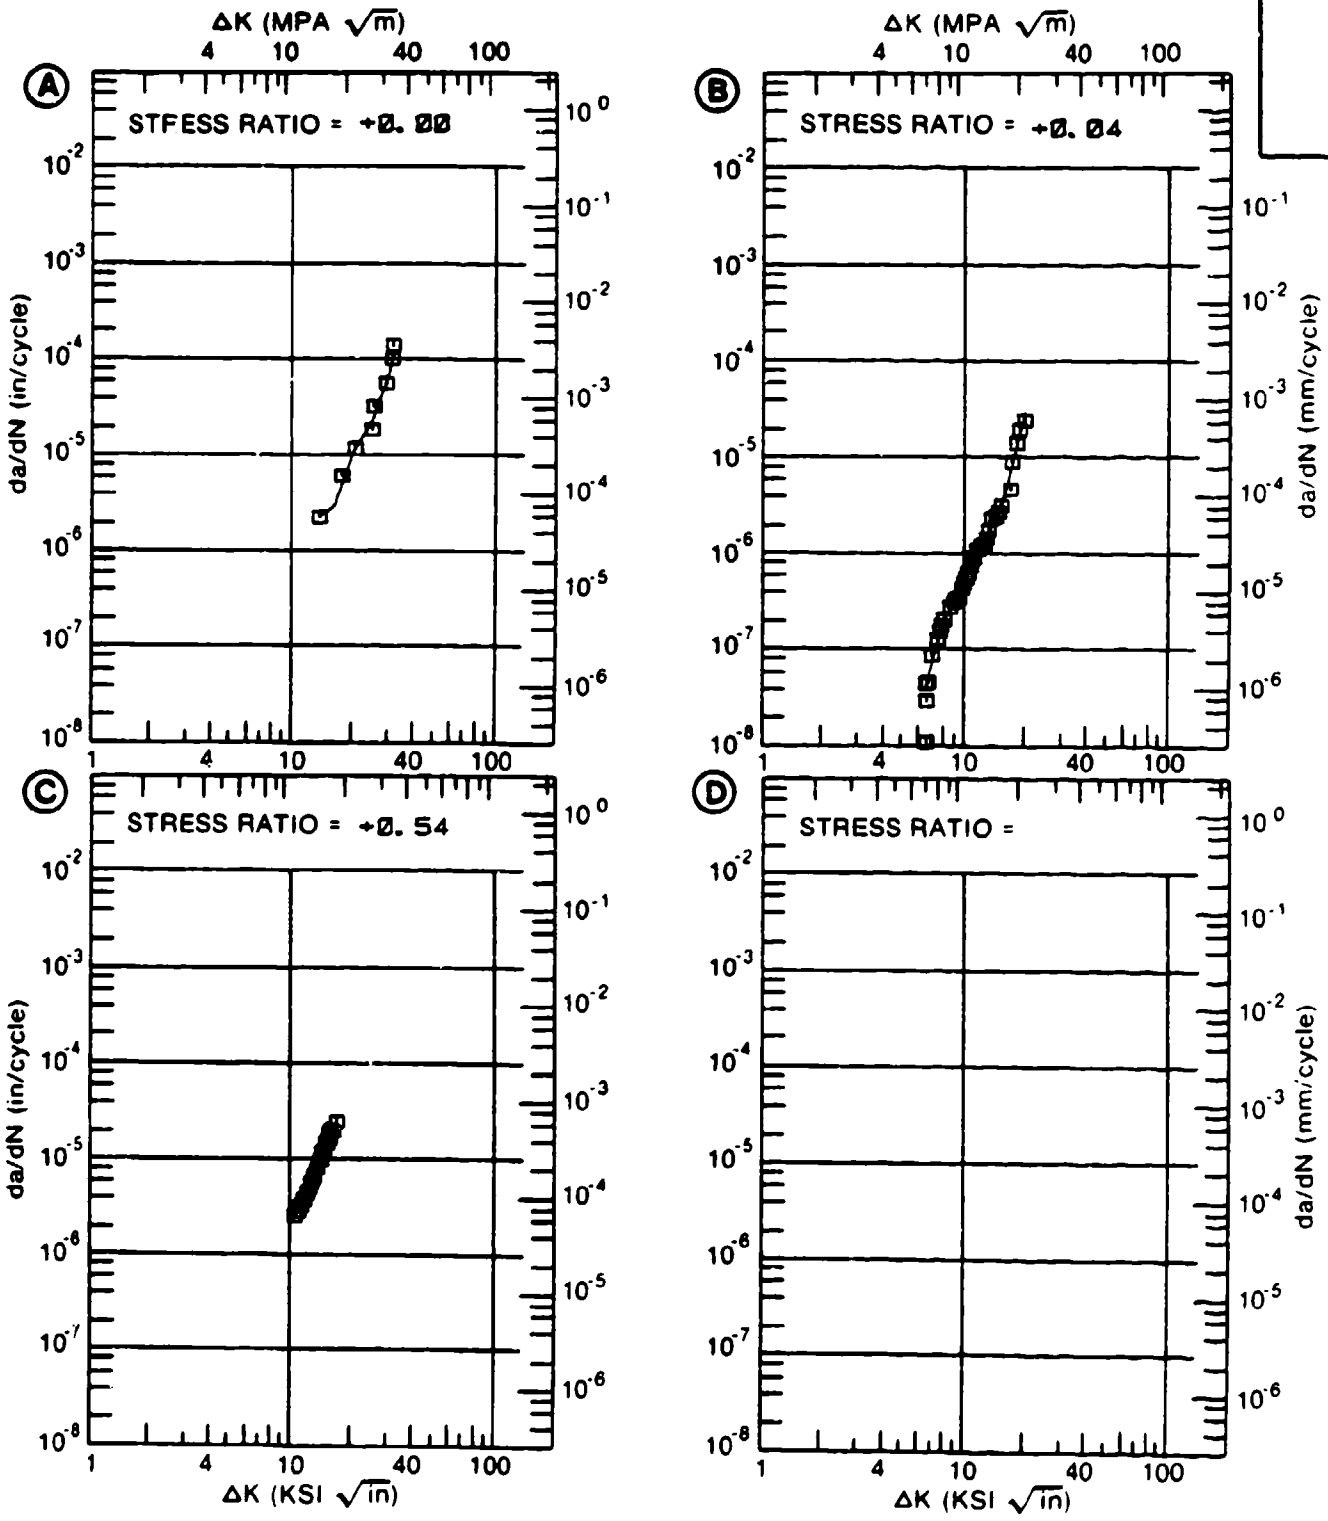


Figure 4.16.3.6

TABLE 4.16.3.7

**FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR**

**DATA ASSOCIATED WITH FIGURE 4.16.3.7 INDICATING EFFECT
OF ENVIRONMENT**

MATERIAL: TITANIUM TI-8AL-1MO-1V
CONDITION: 1830F 1HR WG, 1100F 8HRS AC

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E=+ 800F AIR		
DELTA K MIN	A:	4.09	.0338		
	B:	5.78		.455	
	C:				
	D:				
		5.00	.107		
		6.00	.200	.450	
		7.00	.355	.484	
		8.00	.598	.591	
		9.00	.967	.769	
		10.00	1.50	1.03	
	13.00	4.70	2.51		
	16.00		5.52		
DELTA K MAX	A:	15.89	11.5		
	B:	19.11		10.7	
	C:				
	D:				

ROOT MEAN SQUARE 10.00 8.96
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: 1830F 1HR WQ, 1100F 8HRS AC

FORM: 1.00" TH FORGING

SPECIMEN TYPE: CCP

ORIENTATION: C-R

STRESS RATIO: +0.10

FREQUENCY: 30.00 HZ

YIELD STRENGTH: 135.5- 145.8 KSI

ULT. STRENGTH: 148.5- 159.3 KSI

SPECIMEN THK: 0.078- 0.080"

SPECIMEN WIDTH: 1.750"

REFERENCES: PW002

TITAN.
ALLOY

TI-8AL-
1MO-1V

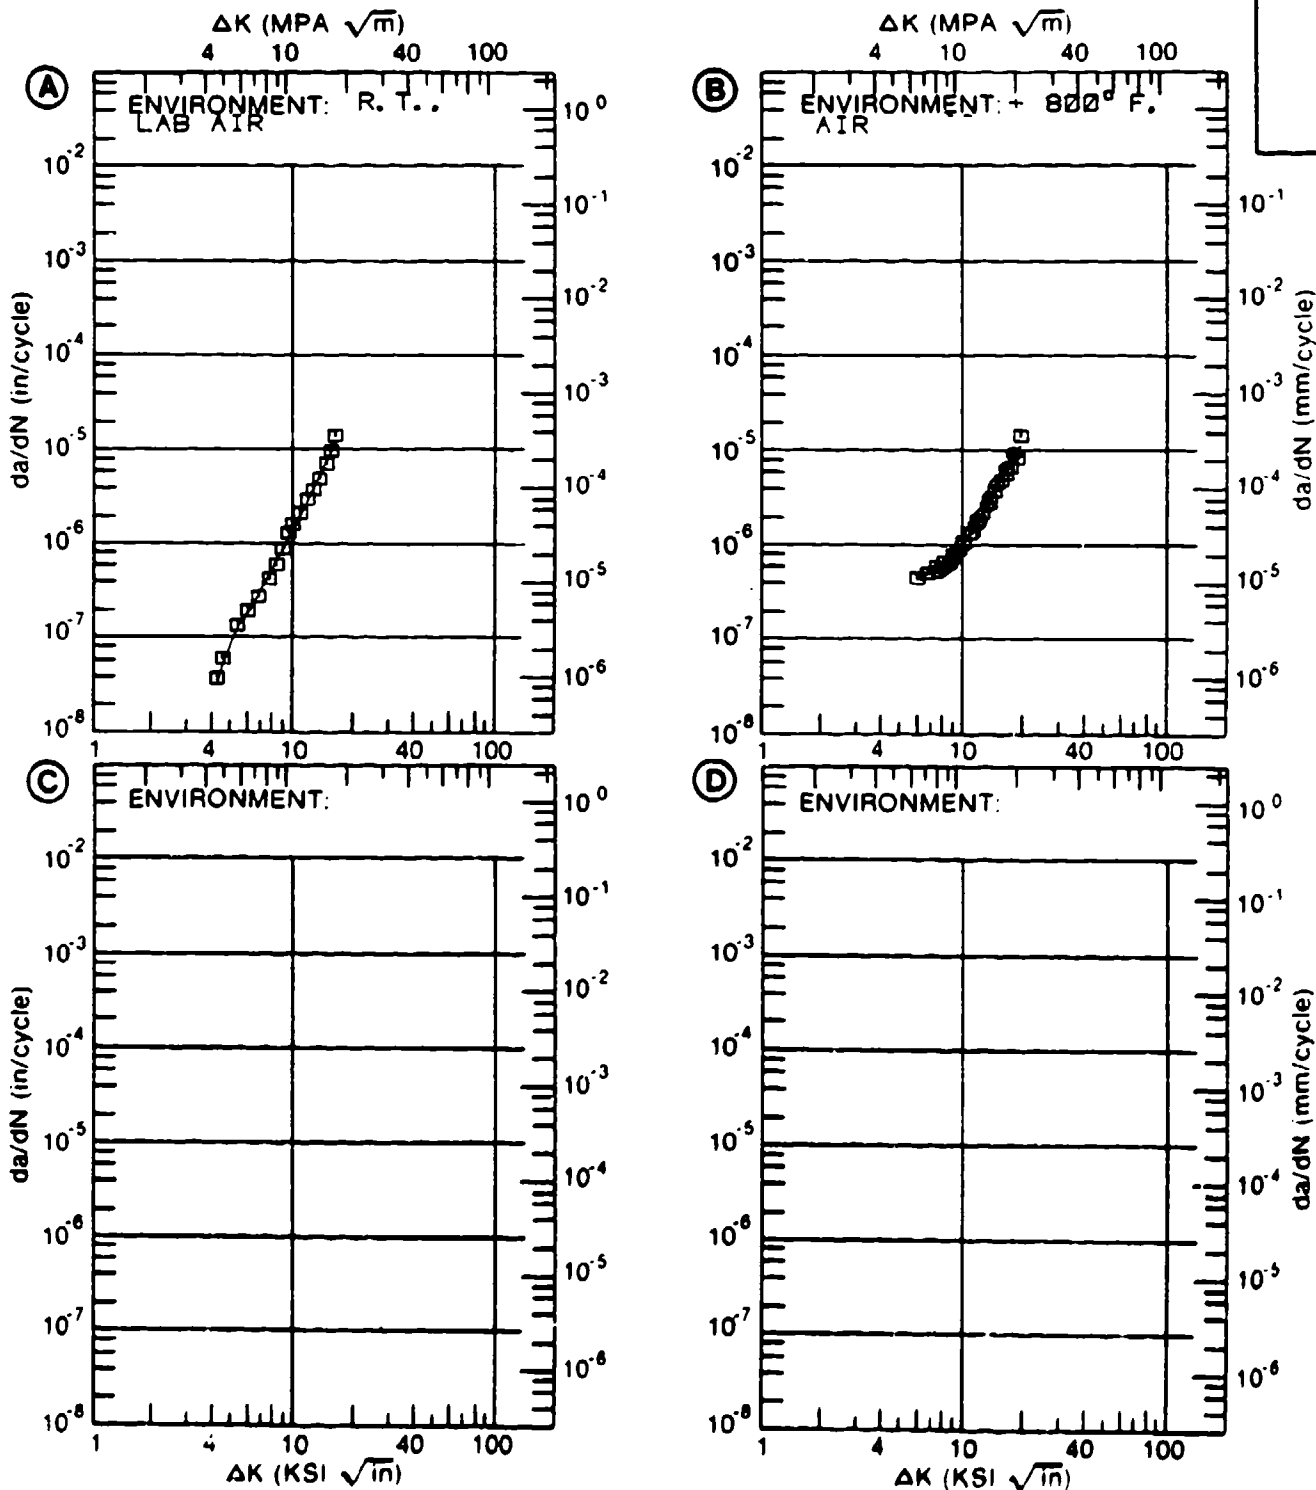


Figure 4.16.3.7

TABLE 4.16.3.8

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.8 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-8AL-1MD-1V			
CONDITION:					
K MAX (KSI*IN**1/2)		DA/DT (10**-3 IN/HOUR)			
		A	B	C	D
		E= DRY CCL4	E= WATER SAT CCL4		
K MAX MIN	A: 28.00	581.			
	B: 29.50		855.		
	C:				
	D:				
	30.00	751.	896.		
	35.00	1259.	1149.		
	40.00	1854.	1358.		
50.00	3149.	2767.			
60.00	4395.	5272.			
70.00	5470.				
K MAX MAX	A: 74.50	5887.			
	B: 67.50		6317.		
	C:				
	D:				
ROOT MEAN SQUARE		19.95	19.48		
PERCENT ERROR					

CONDITION/HT:
 FORM:
 SPECIMEN TYPE: SENT
 ORIENTATION:
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK:
 SPECIMEN WIDTH:
 CRACK LENGTH (A₀):
 K_{ISCC}:
 REFERENCES: 82651

TITAN.
 ALLOY

TI-8AL-
 1MO-1V

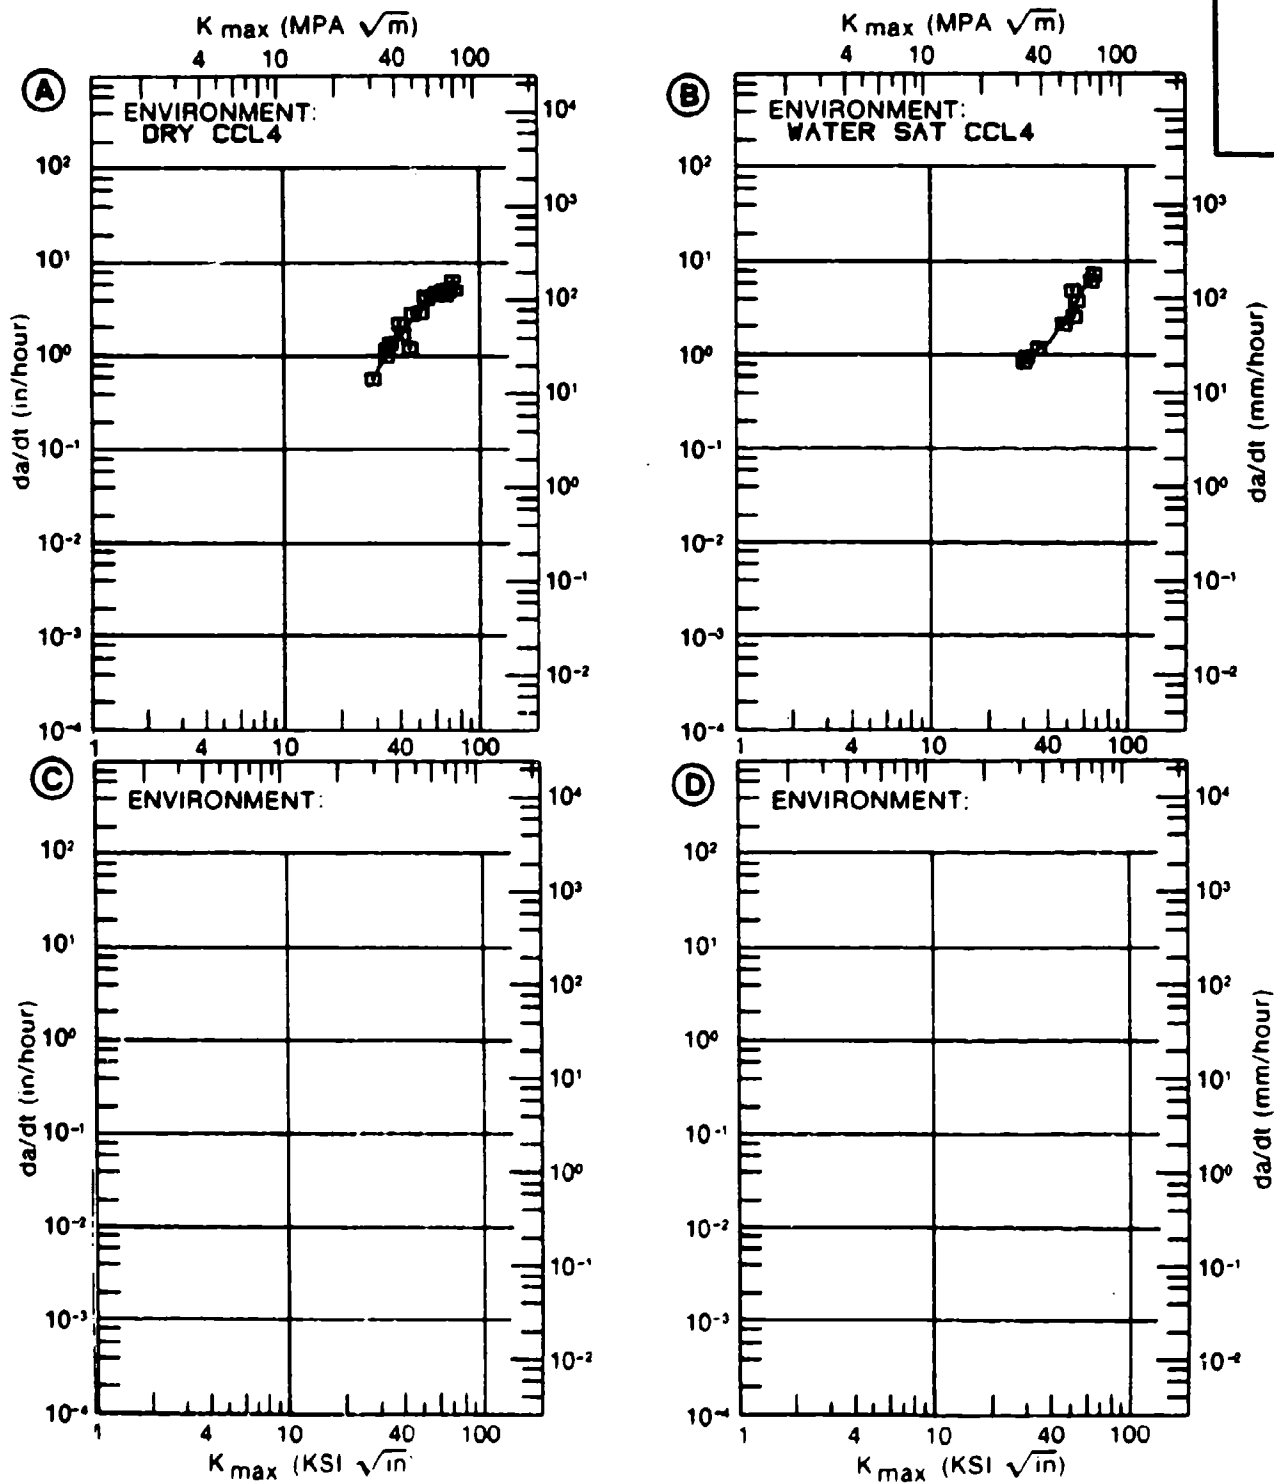


Figure 4.16.3.8

TABLE 4.16.3.9

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.16.3.9 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-BAL-1MO-1V			
CONDITION:					
K MAX (KSI*IN**1/2)		DA/DT (10**-3 IN/HOUR)			
		A	B	C	D
		E= DRY CH2CL2	E= WATER SAT CH2CL2	E= DRY CH2I2	
K MAX	A:				
MIN	B:				
	C:	28.50		1394.	
	D:				
		30.00		1601.	
		35.00		2163.	
		40.00		2507.	
		50.00		2739.	
		60.00		2740.	
K MAX	A:				
MAX	B:				
	C:	70.00		2753.	
	D:				
ROOT MEAN SQUARE		0.00	0.00	1.14	
PERCENT ERROR					

CONDITION/HT:
 FORM:
 SPECIMEN TYPE: SENT
 ORIENTATION:
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK:
 SPECIMEN WIDTH:
 CRACK LENGTH (A_0):
 K_{ISCC} :
 REFERENCES: 92851

TITAN.
 ALLOY

TI-9AL-
 1MO-1V

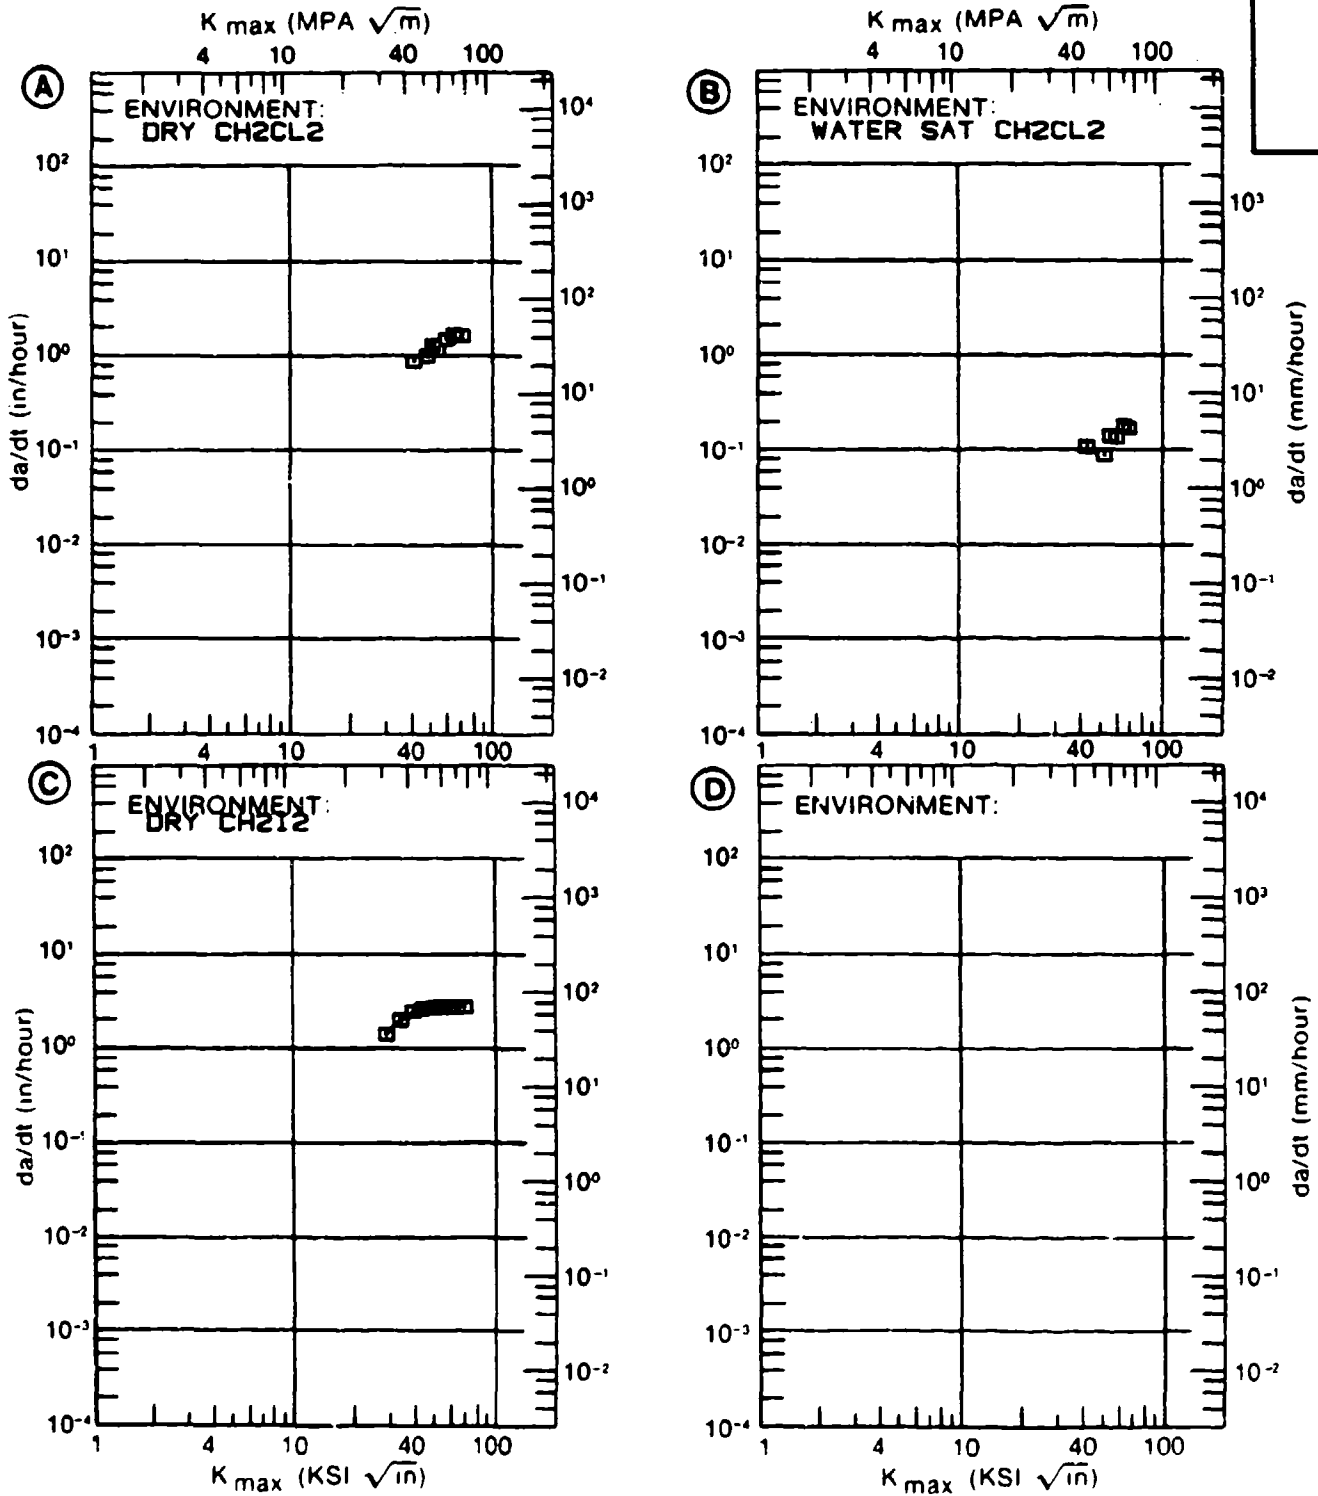


Figure 4.15.3.9

TABLE 4.16.3.10

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 4.16.3.10 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-8AL-1MO-1V			
CONDITION:					
K MAX (KSI*IN**1/2)	A:	DA/DT (10** ⁻³ IN/HOUR)			
		B:	C:	D:	E:
					3. 5% NAACL
K MAX	A:				
MIN	B:				
	C:				
	D:				
		200. 00			
K MAX	A:				
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		0. 00			
PERCENT ERROR					

CONDITION/HT:
 FORM: 0.1" TH SHEET
 SPECIMEN TYPE: SENT
 ORIENTATION:
 YIELD STRENGTH: 150.0 KSI
 ULT. STRENGTH:

SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 3.000"
 CRACK LENGTH (A₀):
 K_{ISCC}: 22.00 KSI (SQRT IN)
 REFERENCES: 77458

TITAN.
 ALLOY
 TI-8AL-
 1MO-1V

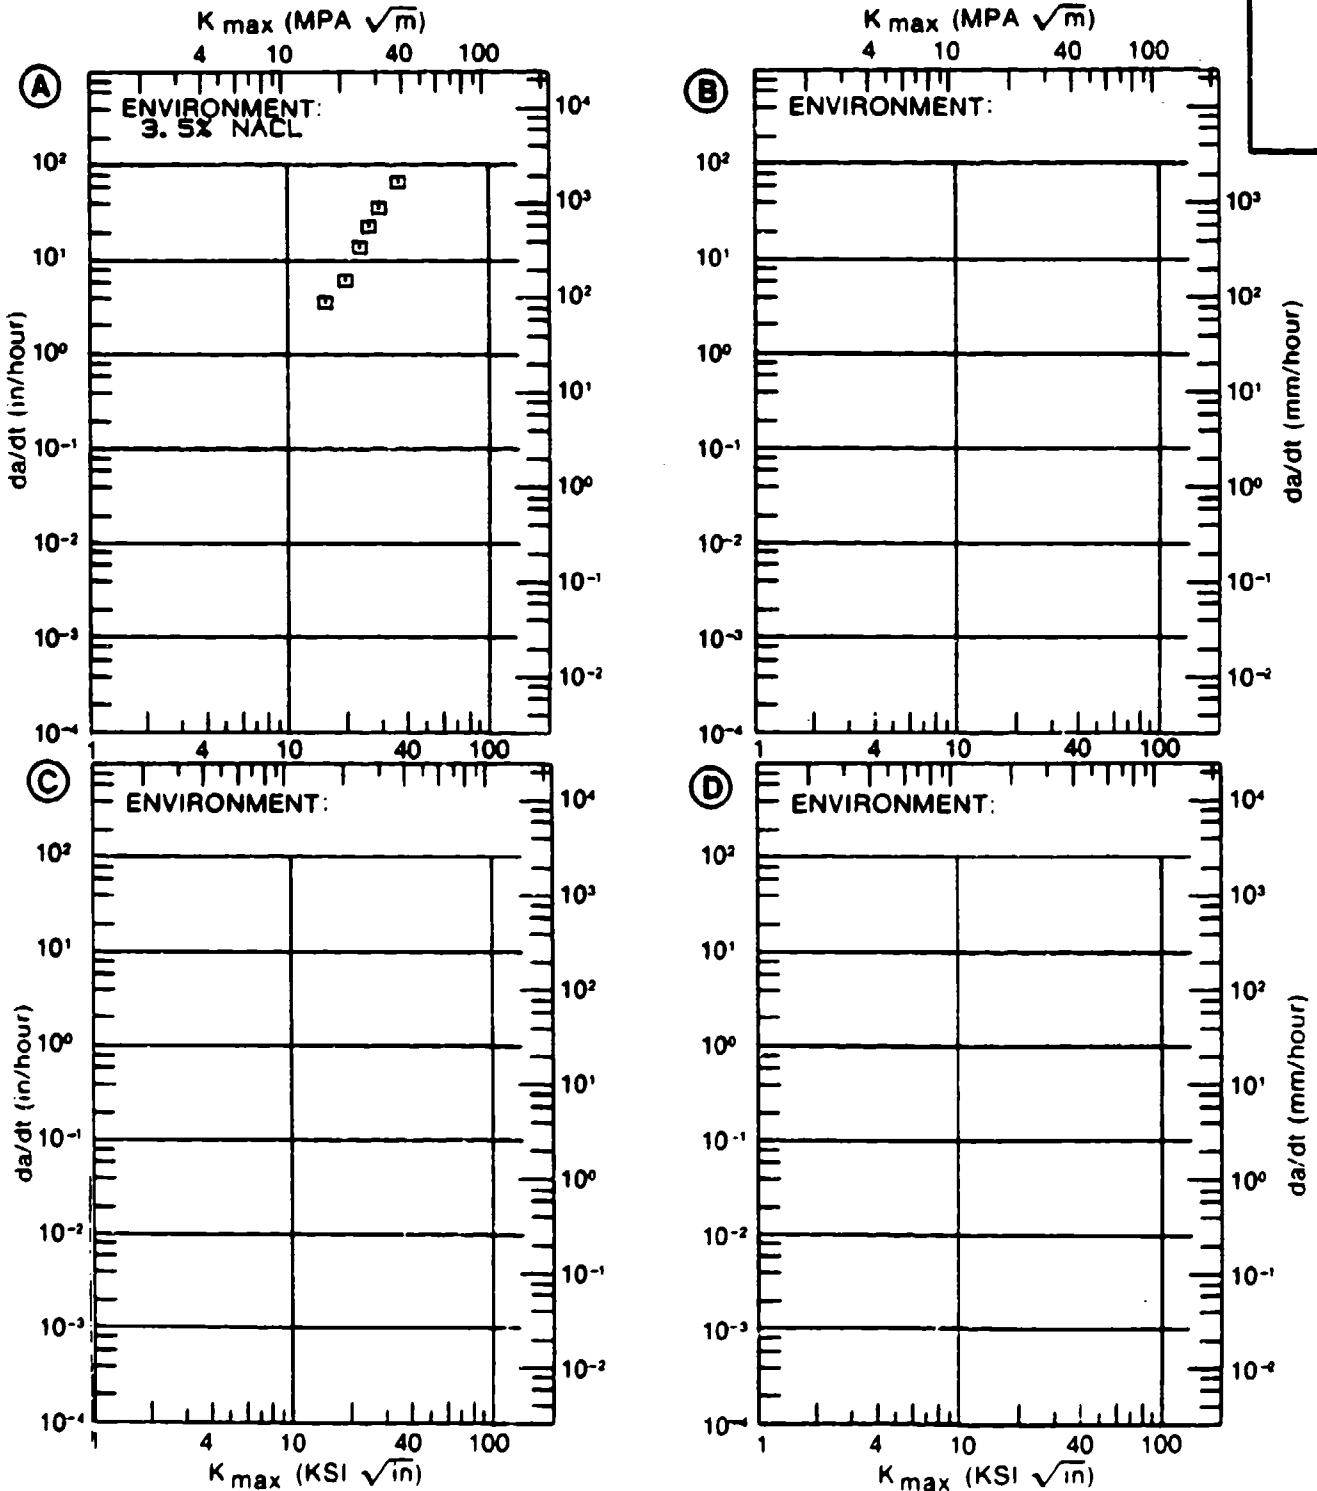


Figure 4.16.3.10

TABLE 4.16.3.11

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.11 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-BAL-1MO-1V			
CONDITION: MA					
K MAX (KSI*IN**1/2)		DA/DT (10** ⁻³ IN/HOUR)			
		A	B	C	D
		E= 3.5% NaCl			
K MAX	A: 20.80	59.2			
MIN	B:				
	C:				
	D:				
	25.00	11168.			
K MAX	A: 29.50	29280.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		59.14			
PERCENT ERROR					

CONDITION/HT: MA
 FORM: 0.1" TH SHEET
 SPECIMEN TYPE:
 ORIENTATION:
 YIELD STRENGTH: 145.0 KSI
 ULT. STRENGTH:

SPECIMEN THK: 0.100"
 SPECIMEN WIDTH: 8.000"
 CRACK LENGTH (A₀):
 K_{ISCC}: 21.00 KSI (SQRT IN)
 REFERENCES: 04290

TITAN.
 ALLOY

TI-BAL-
 1MO-1V

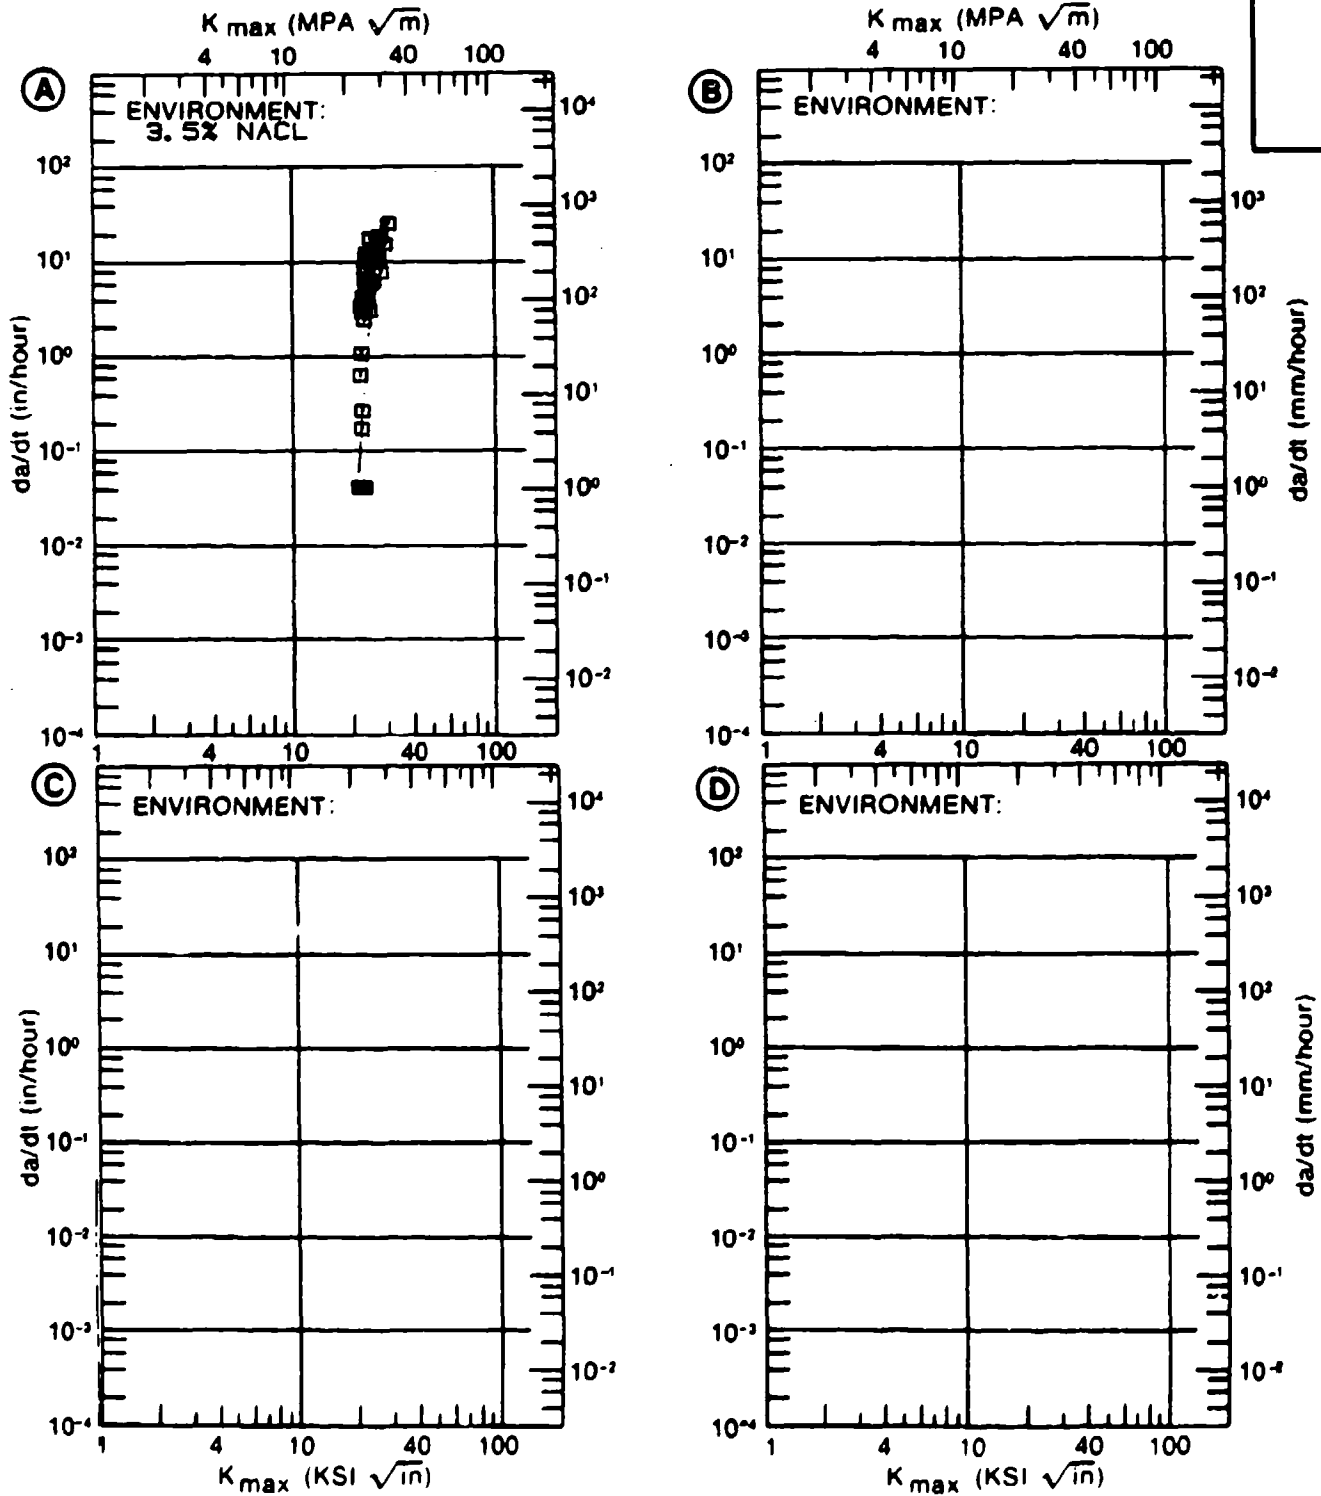


Figure 4.16.3.11

TABLE 4.16.3.12

**SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR**

**DATA ASSOCIATED WITH FIGURE 4.16.3.12 INDICATING EFFECT
OF ENVIRONMENT**

MATERIAL: TITANIUM		TI-BAL-1MO-1V			
CONDITION: MA					
K MAX (KSI*IN**1/2)		DA/DT (10** ⁻³ IN/HOUR)			
		A	B	C	D
		E ⁻⁴ DIST. WATER			
K MAX MIN	A:	20.00	10.0		
	B:				
	C:				
	D:				
		25.00	110.		
		30.00	601.		
		35.00	1289.		
		40.00	1533.		
K MAX MAX	A:	49.00	1610.		
	B:				
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		25.16			

CONDITION/HT: MA
 FORM: B, 2" TH PLATE
 SPECIMEN TYPE: SENT
 ORIENTATION:
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 0.288"
 SPECIMEN WIDTH: 2.888"
 CRACK LENGTH (A₀):
 K_{ISCC}:
 REFERENCES: 01741

TITAN.
 ALLOY

TI-6AL-
 4V

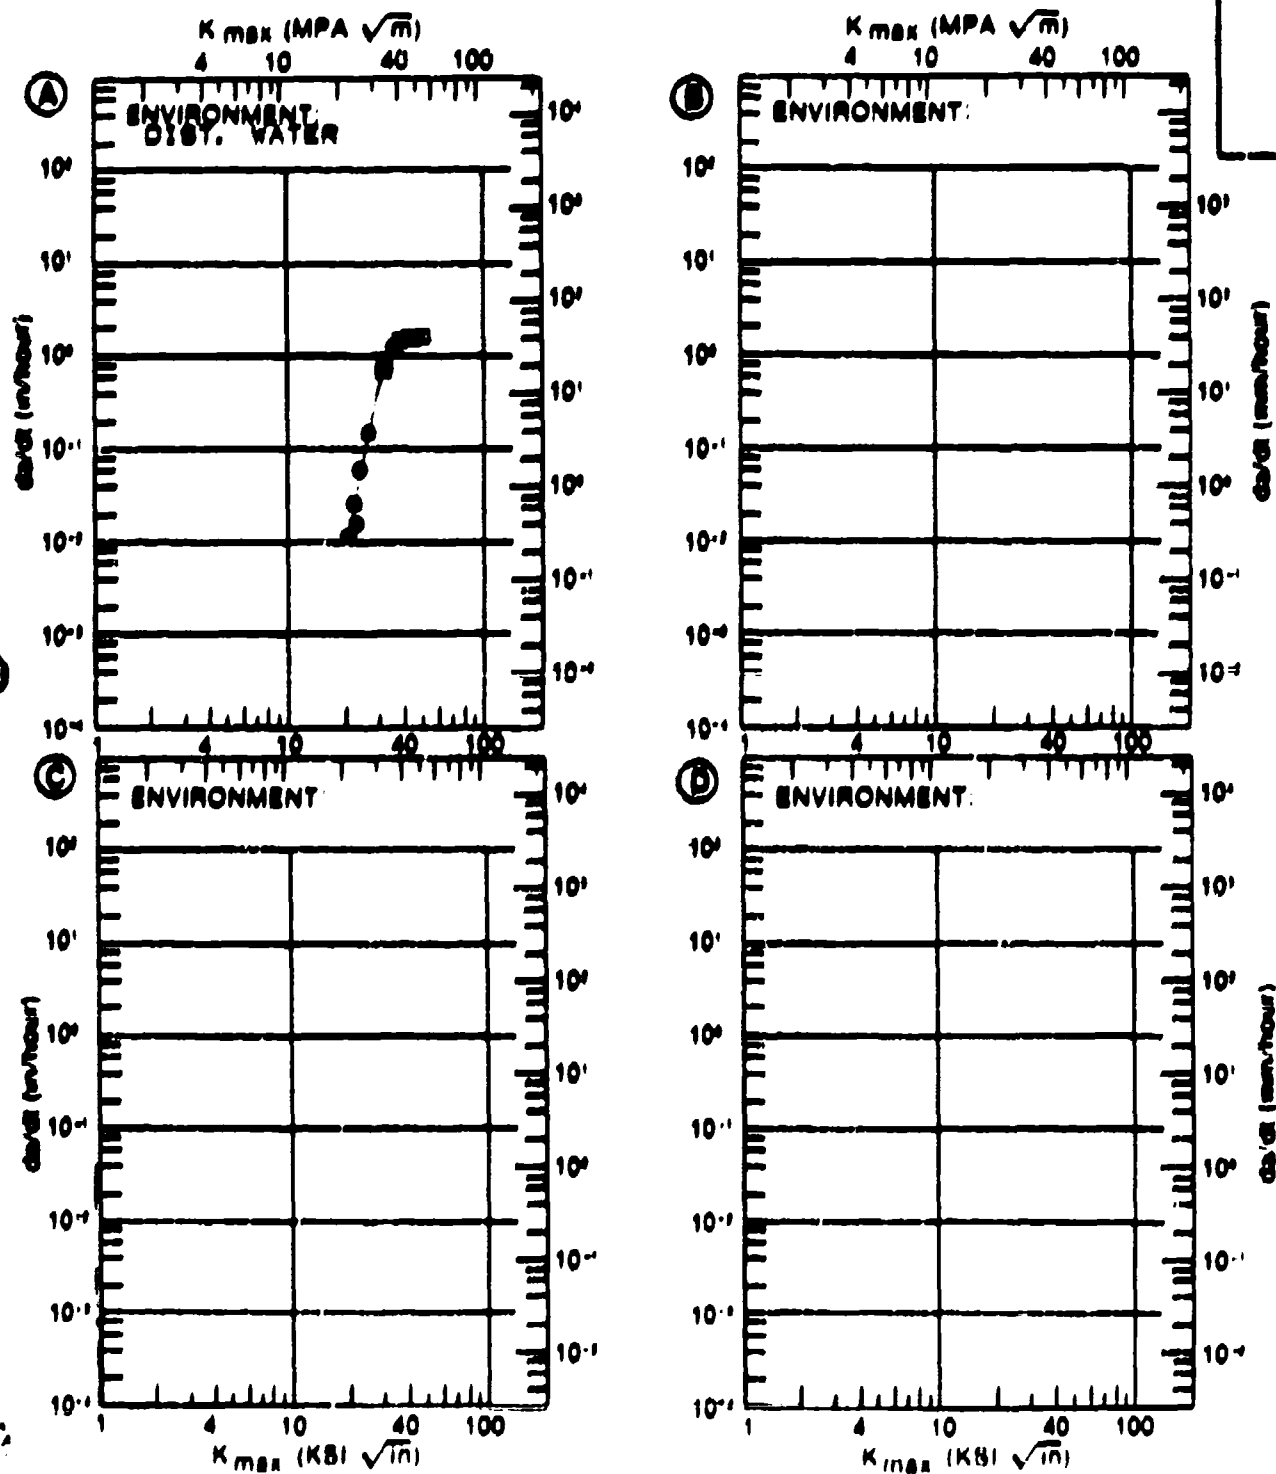


FIGURE 4.16.1.12

TABLE 4.16.3.13

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.13 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-BAL-1MO-1V			
CONDITION: 1520F 1HR WQ					
K MAX (KSI*IN**1/2)		DA/DT (10** ⁻³ IN/HOUR)			
		A	B	C	D
		E= R. T. 9MHCL TICL3	E= R. T. DIST. WATER	E= R. T. METHANOL	
K MAX MIN	A:	16.00	430.		
	B:	26.00		93.3	
	C:	12.00			1.98
	D:	13.00			5.76
		16.00			42.1
		20.00	1875.		129.
		25.00	3467.		192.
		30.00	4989.	182.	197.
		35.00	6257.	330.	188.
		40.00	7222.	488.	189.
	50.00	8360.	672.	256.	
K MAX MAX	A:	60.00	8778.		
	B:	60.00		604.	
	C:	60.00			527.
D:					
ROOT MEAN SQUARE PERCENT ERROR		18.81	10.02	26.51	

CONDITION/HT: 1520F 1HR WQ
 FORM: 0.2" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION:
 YIELD STRENGTH: 124.0 KSI
 ULT. STRENGTH:

SPECIMEN THK: 0.250"
 SPECIMEN WIDTH:
 CRACK LENGTH (A₀):
 K_{ISCC}:
 REFERENCES: 93899

TITAN.
 ALLOY
 TI-8AL-
 1MO-1V

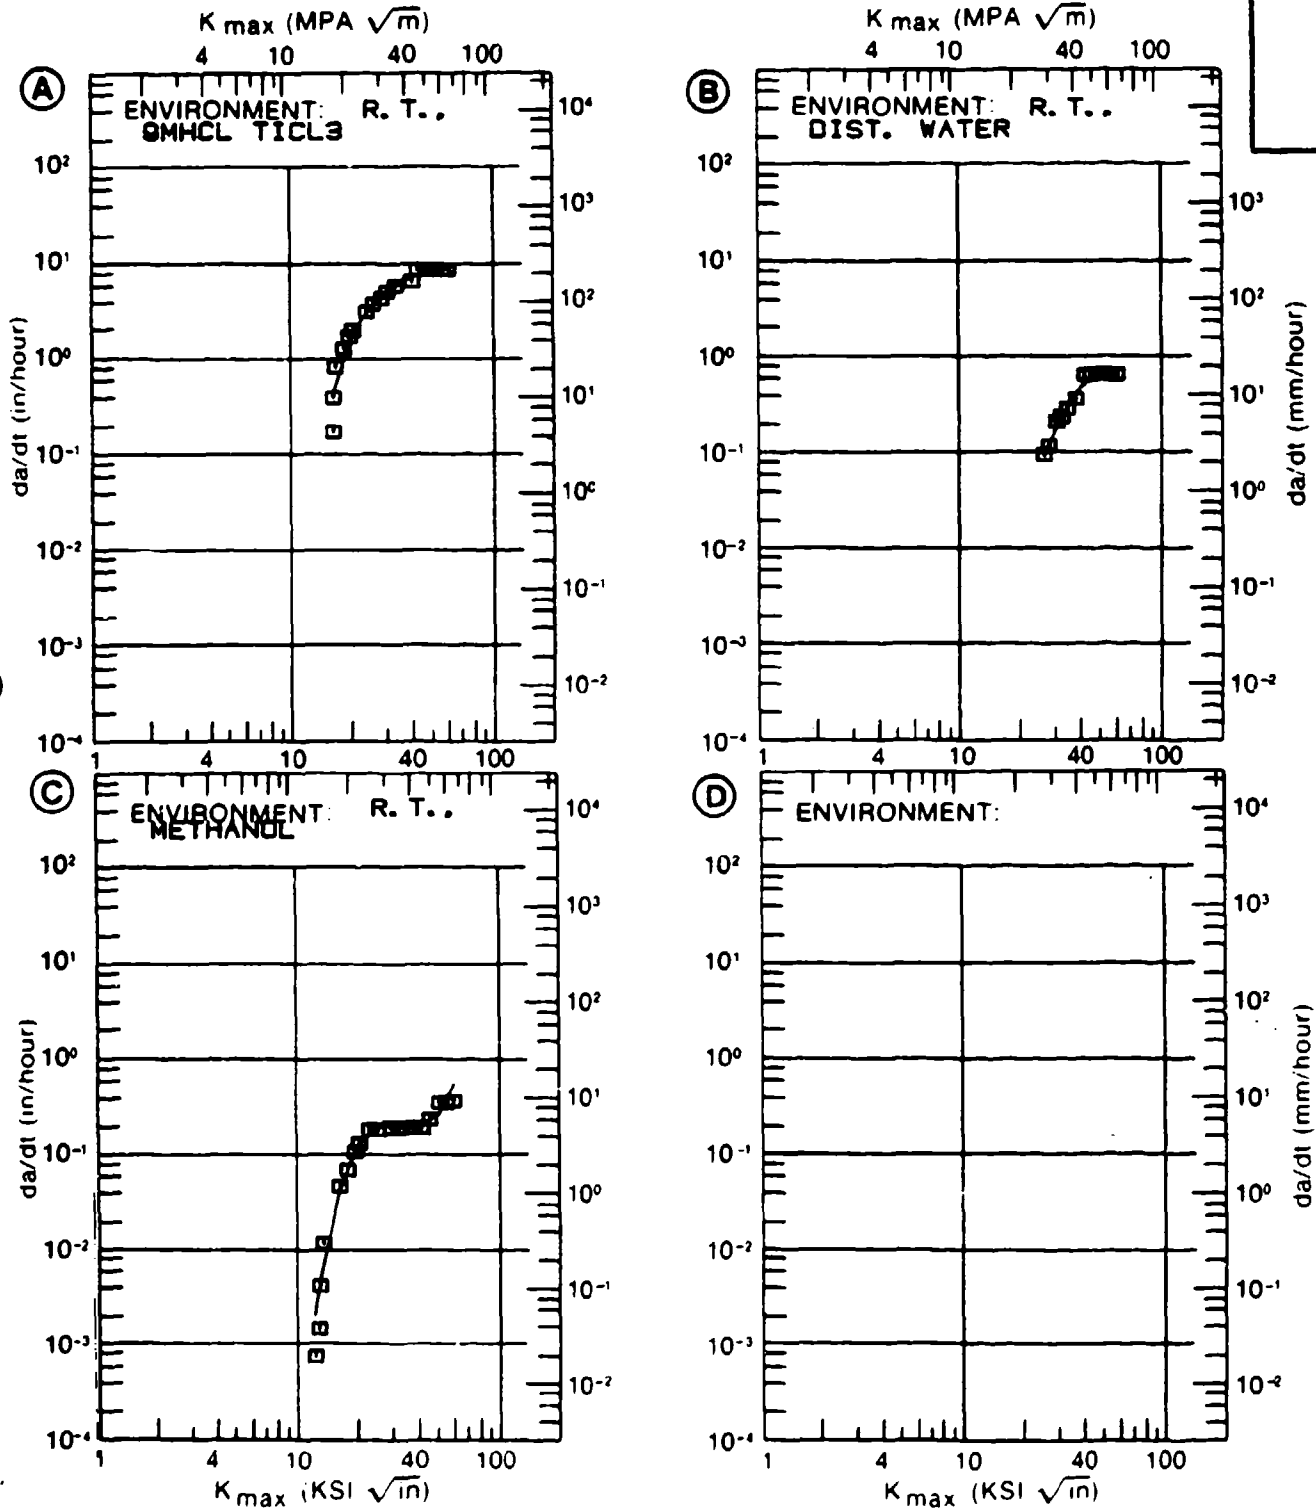


Figure 4.16.3.13

TABLE 4.16.3.14

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.14 INDICATING EFFECT
OF ENVIRONMENT

K MAX (KSI*IN**1/2)		DA/DT (10** ⁻³ IN/HOUR)			
		A	B	C	D
		E= R. T. TI CL4	E= R. T. GLYCERINE	E= R. T. HNO3	
K MAX MIN	A: 16.80	15.2			
	B: 26.00		1.64		
	C: 33.80			1.35	
	D:				
	20.00	23.4			
	25.00	32.1			
	30.00	37.0	1.92		
	35.00	40.3	3.14	1.46	
	40.00	44.0	5.32	2.44	
	50.00	56.3	10.2	6.40	
	D:				
K MAX MAX	A: 60.00	81.2			
	B: 60.00		9.11		
	C: 60.00			7.20	
D:					
ROOT MEAN SQUARE		19.57	18.00	16.69	
PERCENT ERROR					

CONDITION/HT: 1520F 1HR, WD
 FORM: 0.2" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION:
 YIELD STRENGTH: 124.0 KSI
 ULT. STRENGTH:

SPECIMEN THK: 0.250"
 SPECIMEN WIDTH:
 CRACK LENGTH (A₀):
 K_{ISCC}:
 REFERENCES: 03000

TITAN.
 ALLOY
 TI-6AL-
 4V

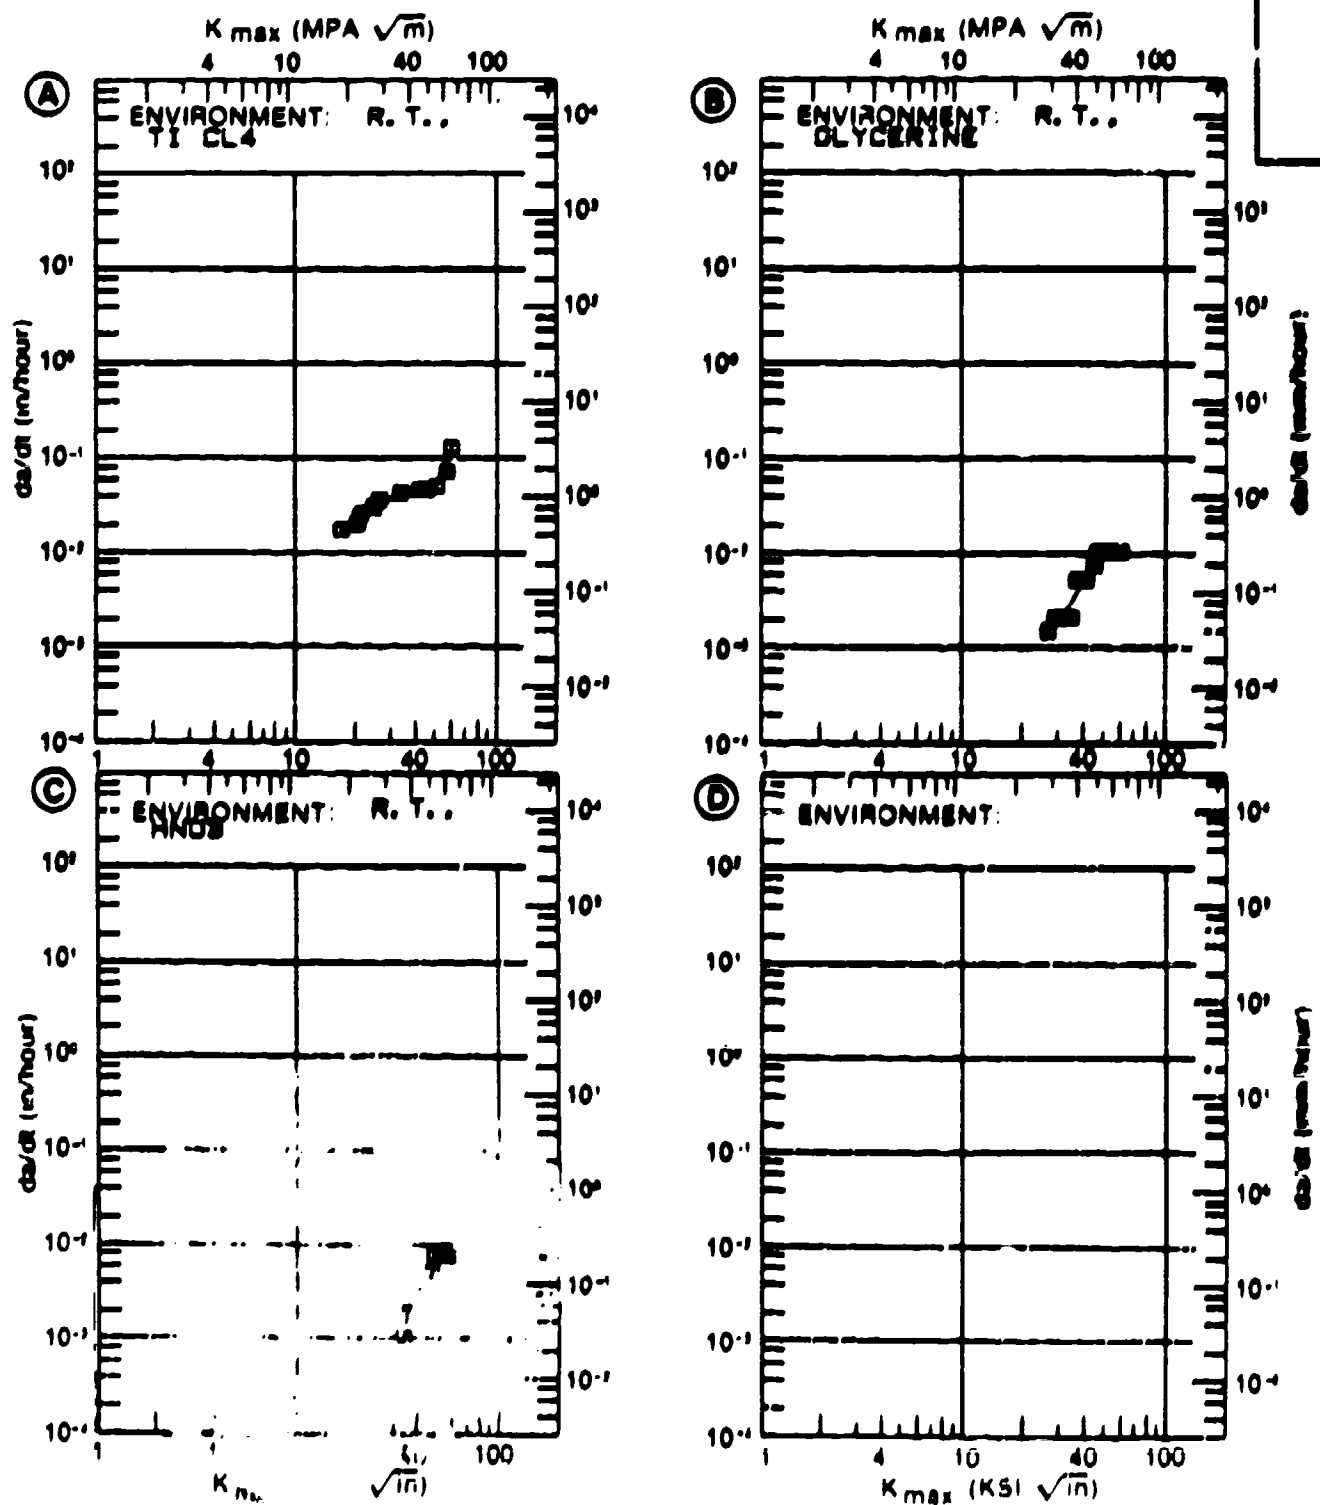


Figure 4.16.3.14

TABLE 4.16.3.15

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.15 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: TITANIUM
CONDITION: 1520F 1HR WQ

TI-8AL-1MO-1V

K MAX
(KSI*IN**1/2)DA/DT (10**⁻³ IN/HOUR)

A

B

C

D

E= R. T.
5H2O/1HCL,
-1000 MVE= R. T.
5H2O/1HCL,
-400 MVE= R. T.
5H2O/1HCL, -200 MVK MAX
MIN
A: 17.00
B: 15.70
C: 19.50
D:

12.6

29.0

5910.

16.00

35.1

20.00

1621.

1310.

25.00

2968.

2062.

30.00

4042.

2828.

35.00

4890.

3618.

40.00

5667.

4463.

50.00

7553.

6750.

5861.

60.00

10704.

9081.

15121.

K MAX
MAX
A: 70.00
B: 68.00
C: 70.00
D:

16458.

11808.

15986.

ROOT MEAN SQUARE
PERCENT ERROR

19.71

20.45

8.15

CONDITION/HT: 1520F 1HR WQ
 FORM: 0.2" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 YIELD STRENGTH: 124.0 KSI
 ULT. STRENGTH:

SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 1.000"
 CRACK LENGTH (A₀): 0.985"
 K_{ISCC}:
 REFERENCES: 83689

TITAN.
 ALLOY

TI-6AL-
 4V

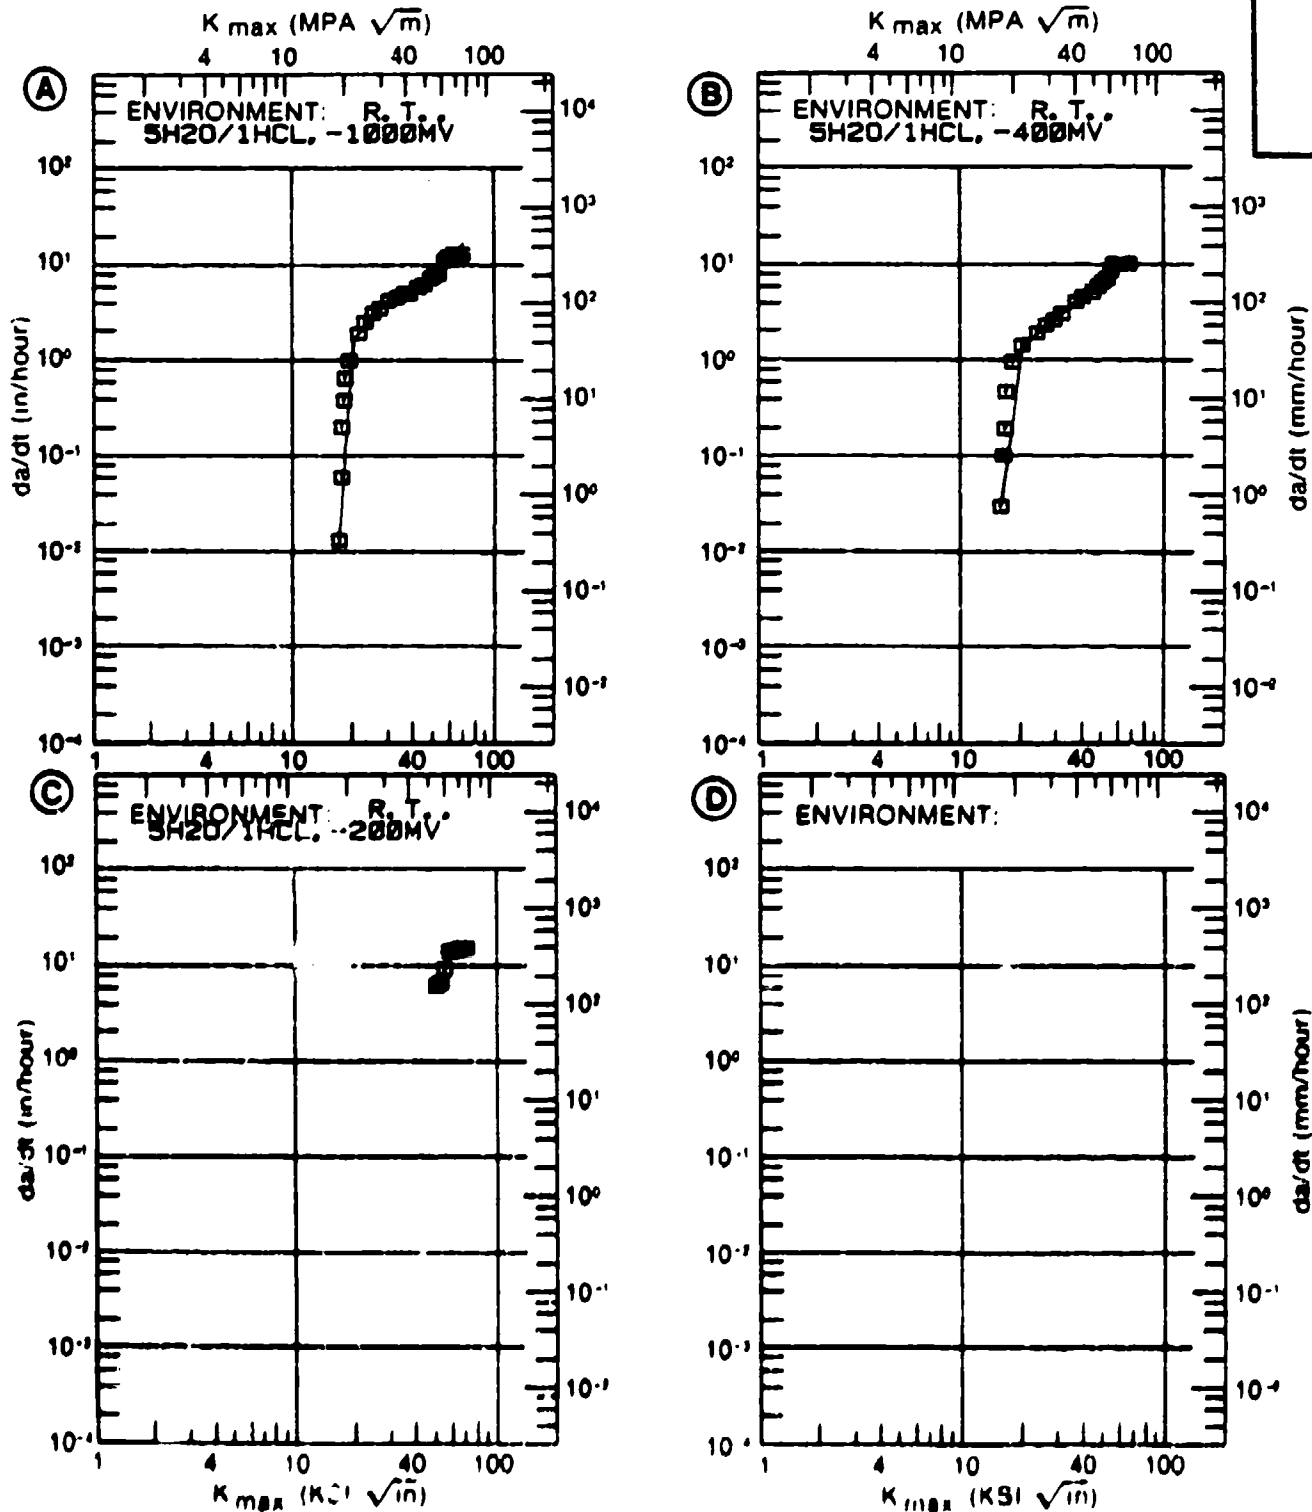


Figure 4.16.3.15

TABLE 4.16.3.16

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.16 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-8AL-1MO-1V			
CONDITION: 1520F 1HR WQ					
K MAX (KSI*IN**1/2)		DA/DT (10** ⁻³ IN/HOUR)			
		A	B	C	D
		E= R. T. 5H2O/1HCL, +500 MV	E= R. T. 5H2O/1HCL, +1000 MV	E= R. T. 5H2O/1HCL, -1.9 TO -1.5	
K MAX	A:				
MIN	B:				
	C:	46.50		4942.	
	D:				
		50.00		5303.	
		60.00		5814.	
K MAX	A:				
MAX	B:				
	C:	70.00		5752.	
	D:				
ROOT MEAN SQUARE		0.00	0.00	1.65	
PERCENT ERROR					

CONDITION/HT: 1520F 1HR WQ
 FORM: 0.2" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: T-L
 YIELD STRENGTH: 124.0 KSI
 ULT. STRENGTH:

SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 1.000"
 CRACK LENGTH (A₀): 0.995"
 K_{ISCC}:
 REFERENCES: 83689

TITAN.
 ALLOY

TI-8AL-
 1MO-1V

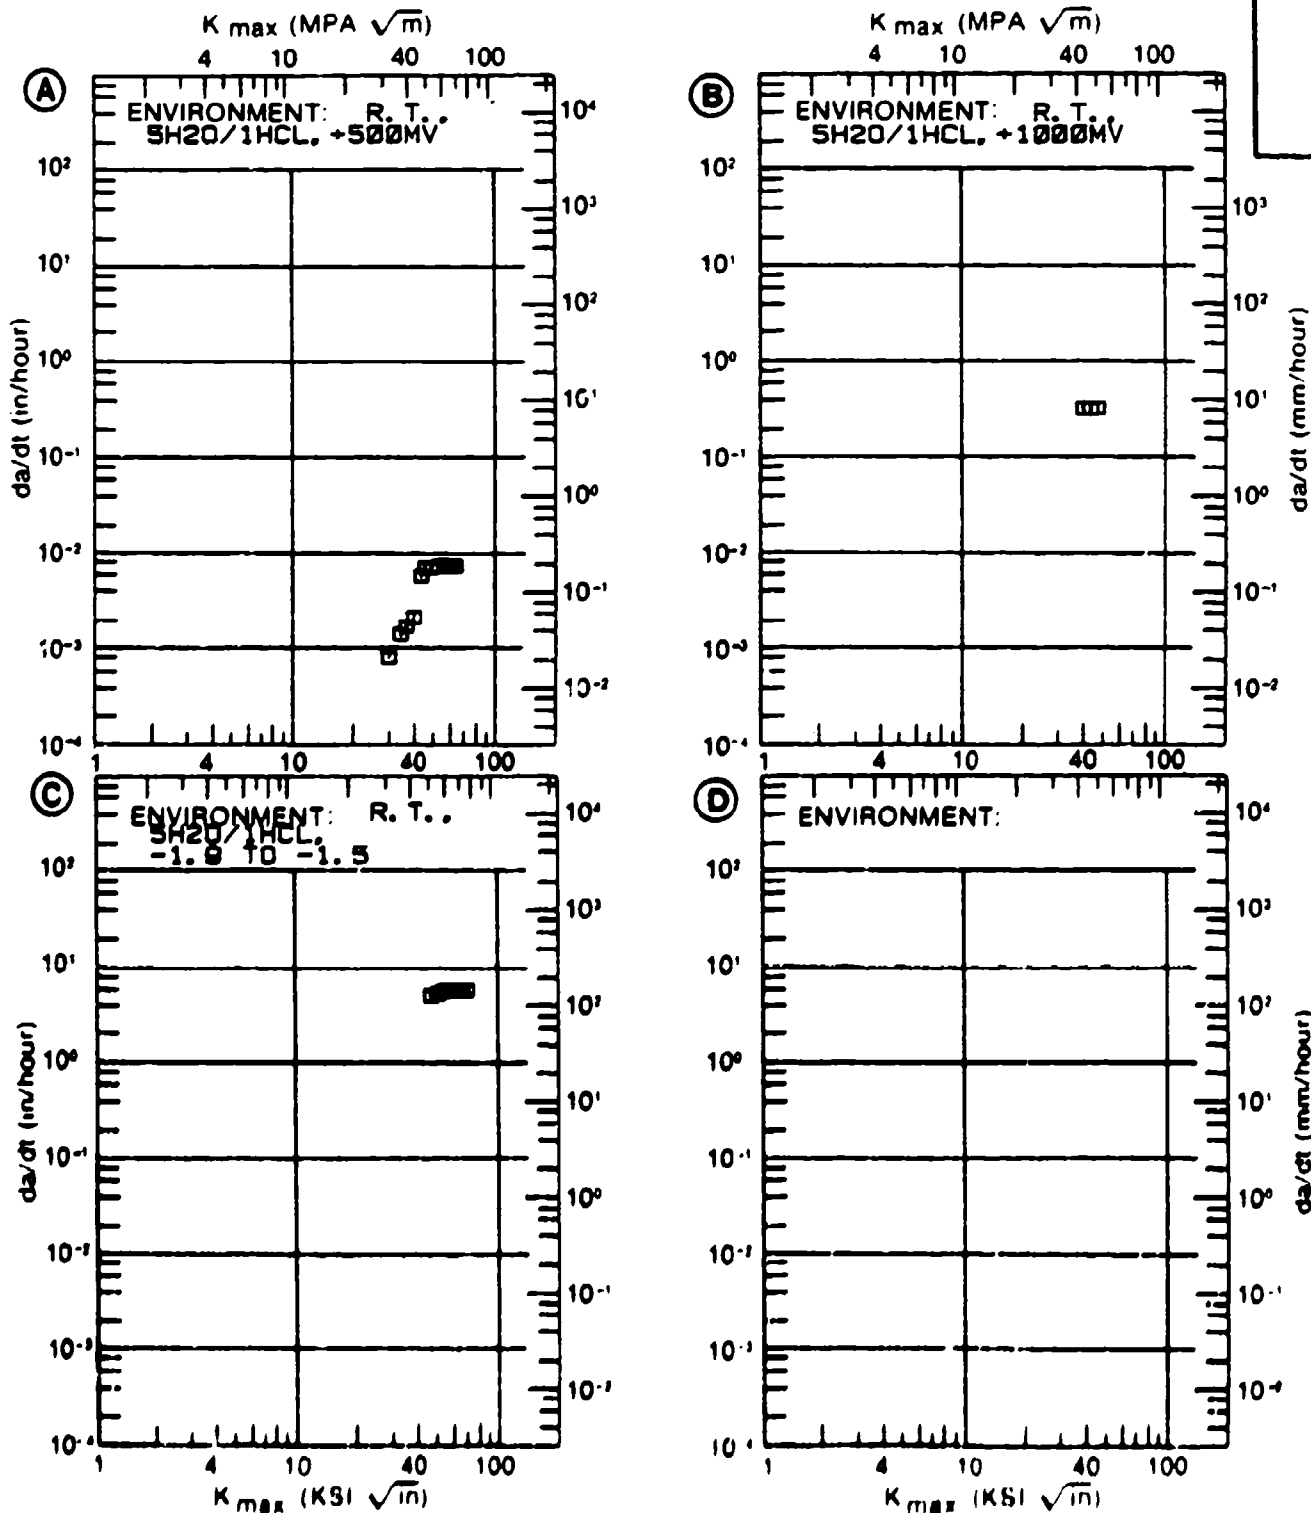


Figure 4.16.3.16

TABLE 4.16.3.17

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.17 INDICATING EFFECT
OF ENVIRONMENT

K MAX (KSI*IN**1/2)		DA/DT (10** ⁻³ IN/HOUR)			
		A	B	C	D
		E= 2100PPM CL 32F	E= 2100PPM CL 72F	E= 2100PPM CL 140F	E= 12100PPM CL 200F
K MAX MIN	A:	21.00	3113.		
	B:	17.00		5014.	
	C:				
	D:				
		20.00		7759.	
		25.00	4963.	11801.	
		30.00	6674.	14738.	
	35.00	7737.	16734.		
	40.00	8432.	18121.		
	50.00	9637.	20090.		
	60.00	11481.			
K MAX MAX	A:	61.00	11729.		
	B:	57.00		21366.	
	C:				
	D:				
ROOT MEAN SQUARE		6.18	3.03	0.00	0.00
PERCENT ERROR					

CONDITION/HT: 1725F FC. 1200F 3HR WQ
 FORM: 0.2" TH PLATE
 SPECIMEN TYPE: CANT
 ORIENTATION: T-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 2.000"
 CRACK LENGTH (A₀): 0.250"
 K_{ISCC}:
 REFERENCES: 85855

TITAN.
 ALLOY

TI-BAL-
 1MO-1V

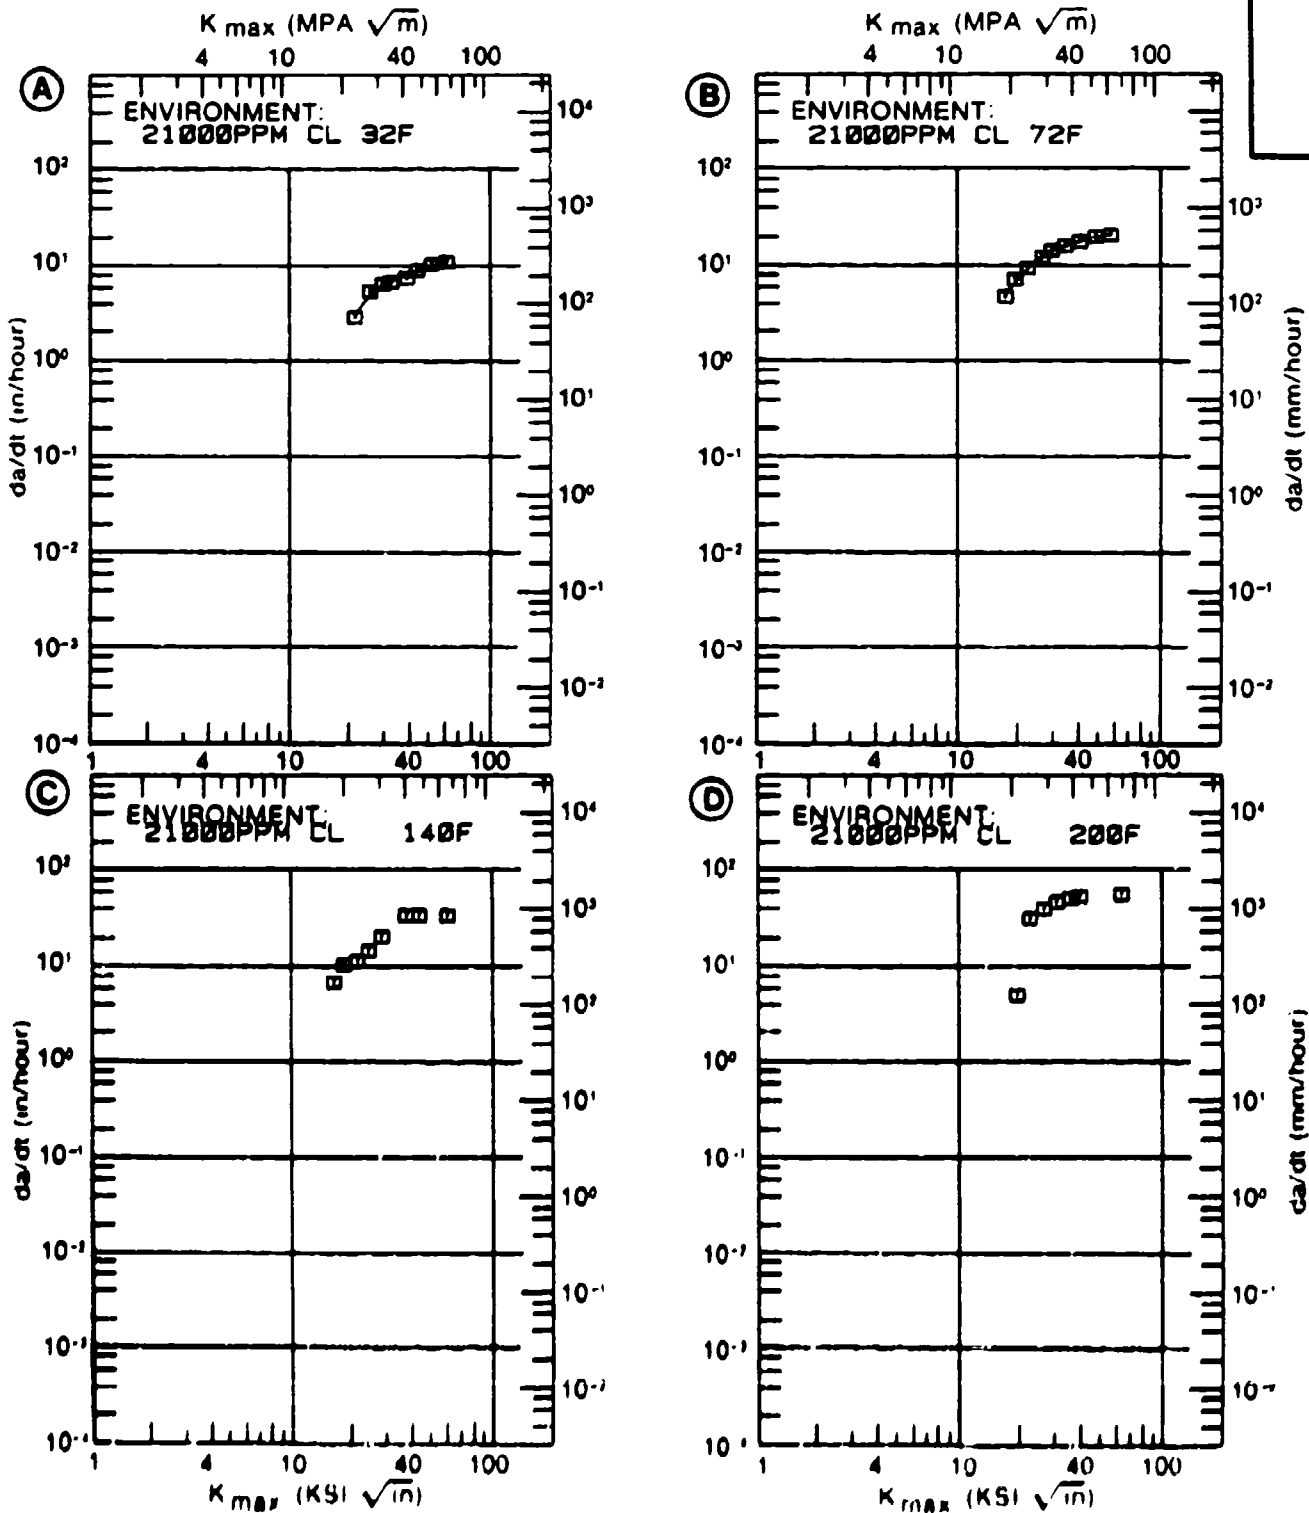


Figure 4.16.3.17

TABLE 4.16.3.18

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 4.16.3.18 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: TITANIUM		TI-BAL.-1M0-1V			
CONDITION: 1725F FC, 1200F 3HR WQ					
K MAX (KSI*IN**1/2)		DA/DT (10**-3 IN/HOUR)			
		A	B	C	D
		E=+ 32F WATER, 0.1PPM CL	E=+ 32F WATER, 100PPM CL	E=+ 32F WATER, 6000PPM CL	E=+ 32F WATER, 21000PPM CL
K MAX MIN	A:				
	B:				
	C: 22.00			4288.	
	D: 16.00				4246.
	20.00				6984.
	25.00			7535.	12536.
	30.00			11710.	15437.
	35.00			13591.	16541.
	40.00			14216.	17074.
	50.00			15481.	19061.
K MAX MAX	A:				
	B:				
	C: 58.00			18718.	
	D: 58.00				23086.
ROOT MEAN SQUARE		0.00	0.00	7.67	13.28
PERCENT ERROR					

CONDITION/HT: 1725F FC, 1200F 3HR WQ
 FORM: 0.2" TH PLATE
 SPECIMEN TYPE: CANT
 ORIENTATION: T-L
 YIELD STRENGTH: 150.0 KSI
 ULT. STRENGTH:

SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 2.000"
 CRACK LENGTH (A₀): 0.250"
 K_{ISCC}:
 REFERENCES: 05055

TITAN.
 ALLOY

TI-8AL-
 1MO-1V

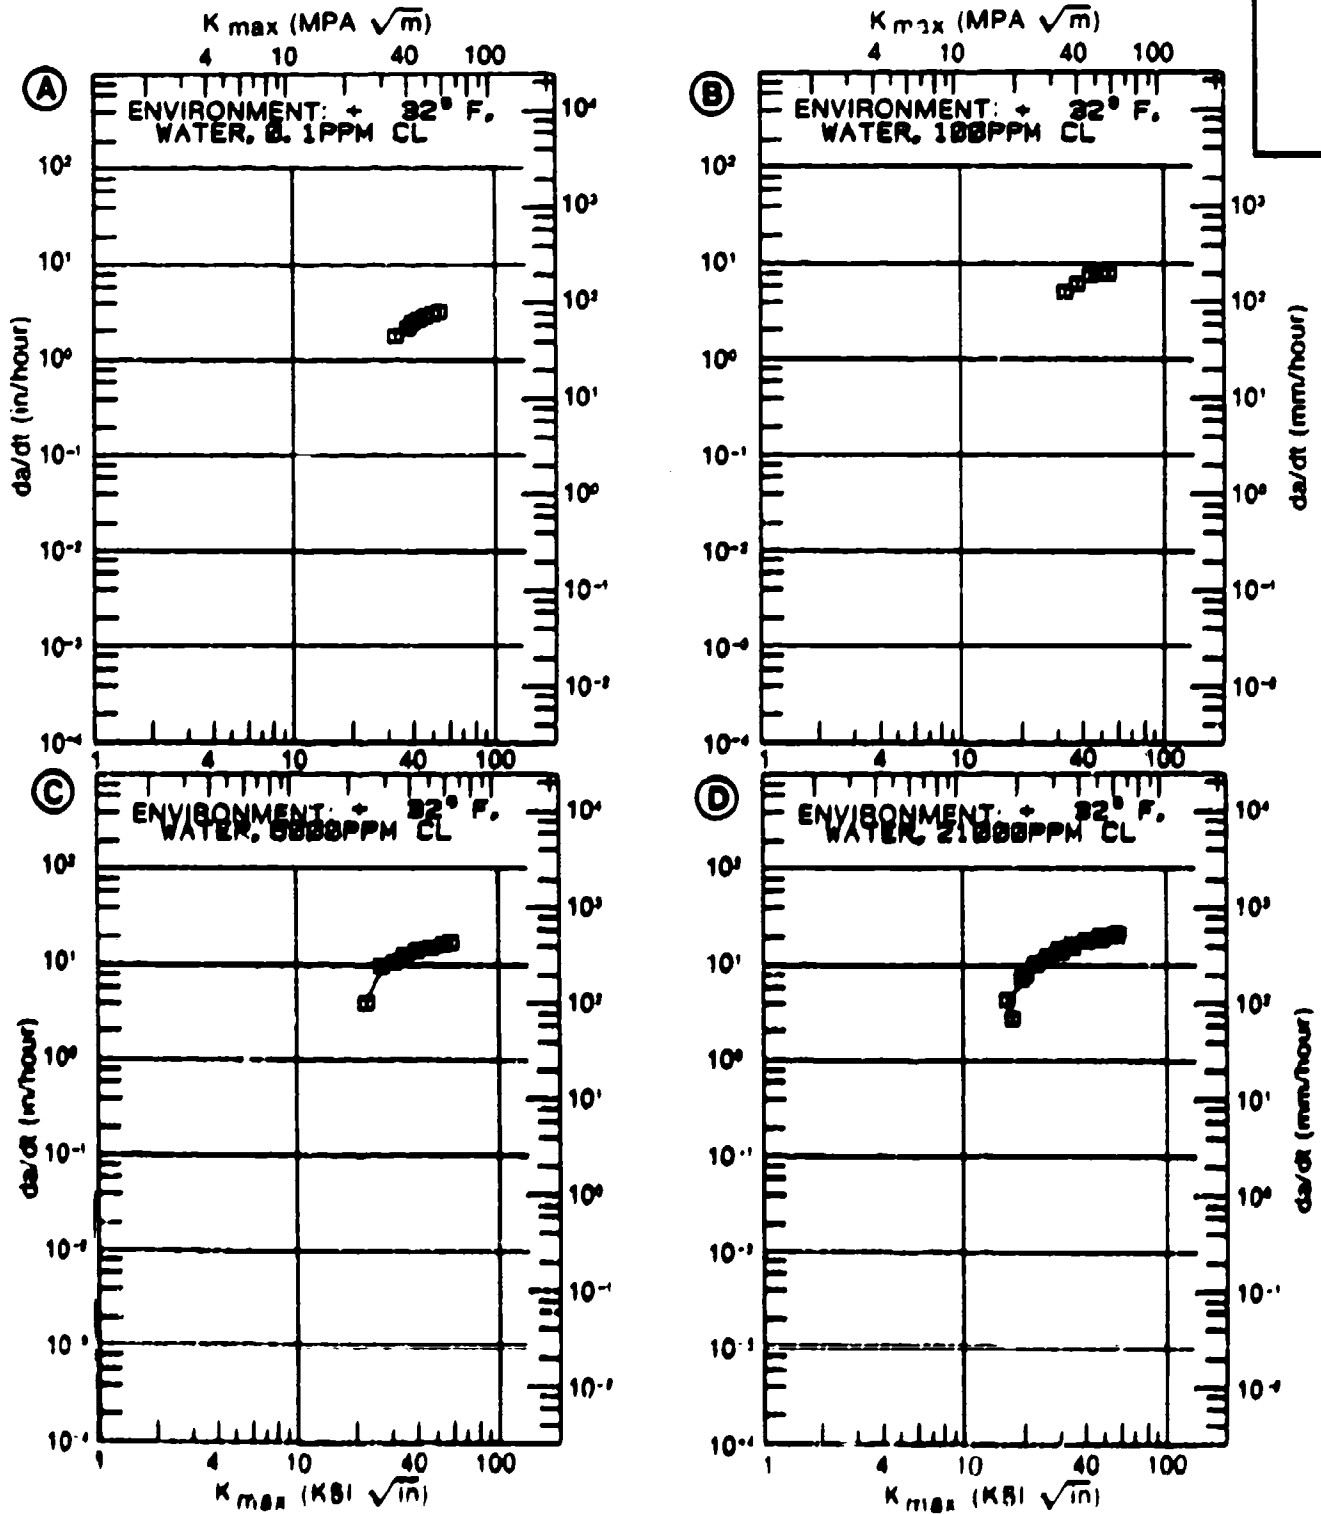


Figure 4.16.3.14

TABLE 4.16.3.19

TITANIUM		TI-6AL-4V2		K15CC1		K15CC2		K15CC3		K15CC4		K15CC5		K15CC6		K15CC7		K15CC8		K15CC9		K15CC10	
PRODUCT FROM	TEST SPEC	YIELD	TEMP	ENVIRONMENT	WIDTH	SPECIFIER	THICK	POSITION	LENGTH	K(1)	K(2)	K(3)	K(4)	K(5)	K(6)	K(7)	K(8)	MEAN	STAN	TEST	DATE	REFER	
(IN)	(F)	(KSI)	(F)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(MIN)			
S	0 13	RT	1-5	130	0 3 5	PCT	MACL	1 000	0 125	CANT	---	54 00	18 00	---	---	---	---	---	---	---	1967	70931	
P	---	RT	---	---	3 5	PCT	MACL	---	---	CANT	---	100 00	38 00	---	---	---	---	---	---	---	1967	70887	
P	0 50	RT	1-5	---	3 5	PCT	MACL	---	---	MB	---	43 00	20 00	---	---	---	---	---	---	---	1969	75386	
P	1 00	RT	1-5	125	0 3 5	PCT	MACL	1 000	0 150	CANT	---	75 00	46 00*	---	---	---	---	---	---	---	1967	84327	
P	1 00	RT	---	125	0	---	---	1 000	0 250	CANT	---	75 00	38 00	---	---	---	---	---	---	---	1967	84327	
P	1 00	RT	---	125	0	---	---	1 000	0 250	CANT	---	75 00	41 00*	---	---	---	---	---	---	---	1967	84327	
P	1 00	RT	---	125	0	---	---	1 000	0 500	CANT	---	83 00	41 00	---	---	---	---	---	---	---	1967	84327	
P	1 00	RT	---	125	0	---	---	1 000	0 500	CANT	---	83 00	41 00	---	---	---	---	---	---	---	1967	84327	
P	1 00	RT	---	125	0	---	---	1 000	1 000	CANT	---	83 00	38 00	---	---	---	---	---	---	---	1967	84327	
P	1 00	RT	---	125	0	---	---	1 000	1 000	CANT	---	83 00	37 00	---	---	---	---	---	---	---	1967	84327	
P	0 10	RT	1-5	130	0 3 5	PCT	MACL	3 000	0 125	SEMT	---	53 50	22 00*	>	60	---	---	---	---	---	1967	71936	
P	0 16	RT	---	145	0	---	---	0 000	0 140	CNT	---	0 000	35 00	21 00	---	---	---	---	---	---	1967	70733	
P	---	RT	1-4	130	0	MECHAN	---	1 000	0 270	CANT	---	45 00	34 00	---	---	---	---	---	---	---	1968	84326	
P	---	RT	---	135	0	---	---	1 000	0 270	CANT	---	44 00	34 00	---	---	---	---	---	---	---	1968	84326	
P	---	RT	1-4	125	0	RETAINED	---	1 000	0 270	CANT	---	44 00	23 00	---	---	---	---	---	---	---	1968	84326	
P	---	RT	---	125	0	---	---	1 000	0 270	CANT	---	102 00	22 00	---	---	---	---	---	---	---	1968	84326	
P	---	RT	---	125	0	---	---	1 000	0 270	CANT	---	43 00	23 00	---	---	---	---	---	---	---	1968	84326	
P	---	RT	1-4	125	0 3 5	PCT	MACL	1 000	0 270	CANT	---	102 00	27 00	---	---	---	---	---	---	---	1968	84326	
P	---	RT	---	125	0	---	---	1 000	0 270	CANT	---	44 00	23 00	---	---	---	---	---	---	---	1968	84326	
P	---	RT	---	125	0	---	---	1 000	0 270	CANT	---	43 00	23 00	---	---	---	---	---	---	---	1968	84326	
P	0 25	31	1-4	124	0 5 10	SILVER	TO	1 000	0 250	BOC	---	0 900	93 00	20 00	---	---	---	---	---	---	1963	80487	
P	0 25	15	1-4	124	0	WATER	LNOL	1 000	0 250	BOC	---	0 900	93 00	22 70	---	---	---	---	---	---	1963	80487	

NOTE: DATA WHICH DO NOT MEET MINIMUM SPECIFIER TENSILE REQUIREMENTS OF 2.5K15CC1/TVS15A180

TABLE 4.16.3.19 (Con't)

COMPTON	PART NO	QTY	UNIT	NEW SPEC	FIELD	TITANIUM	71-84-880-14		8118001		CHECK	STAMP	DATE	REFER
							71-84-880-14	8118001	71-84-880-14	8118001				
							WGT	LEN	WGT	LEN				
							1.000	0.250	0.03	0.485	93.00	19.40		1962
							1.000	0.250	0.03	0.485	93.00	20.30		1962
							1.000	0.250	0.03	0.485	93.46	17.00		1962
							1.000	0.250	0.03	0.485	93.00	23.10		1962
							1.000	0.250	0.03	0.485	93.00	26.00		1962
							1.000	0.250	0.03	0.485	93.00	21.00		1962
							1.000	0.250	0.03	0.485	93.00	19.00		1962
							1.000	0.250	0.03	0.485	93.00	26.00		1962
							1.000	0.250	0.03	0.485	93.00	19.00		1962
							1.000	0.250	0.03	0.485	93.00	27.00		1962
							1.000	0.250	0.03	0.485	93.00	13.00		1962
							1.000	0.250	0.03	0.485	93.00	13.00		1962
							1.000	0.250	0.03	0.485	93.00	23.00		1962
							1.000	0.250	0.03	0.485	93.00	20.00		1962
							1.000	0.250	0.03	0.485	93.00	20.00		1962
							1.000	0.250	0.03	0.485	93.00	20.00		1962

NOTE: DATA BASED ON NET WEIGHT SPECIFIED REQUIREMENTS OF 2.318301/TVS/1224882

TABLE 4.16.3.19 (Con't)

COMPOSITION	FURN	THICK (IN)	TEST TEMP (°F)	SPEC YIELD OR STR (KSI)	ENVIRONMENT	TENSILE		ELONGATION		CRACK LENGTH (IN)	R (SECC)	MEAN REV	TEST TIME (MIN)	DATE PEPER
						W	B	(%)	(%)					
1507 100 MB P	0.25	0.1	1-1	124	0 WATER L10L 110L3	1.000	0.250	0.05	75.00	0.00	16.20	---	1962	82687
1508 100 MB P	0.25	0.1	1-1	124	0 WATER L10L	1.000	0.250	0.05	75.00	0.00	19.20	---	1962	82687
1509 100 MB P	0.25	0.1	1-1	124	0 WATER L10L	1.000	0.250	0.05	75.00	0.00	14.70	---	1962	82687
1510 100 MB P	0.25	0.1	1-1	124	0 WATER L10L -300HV	1.000	0.250	0.05	75.00	0.00	15.20	---	1962	82687
1511 100 MB P	0.25	0.1	1-1	124	0 WATER L10L -100HV	1.000	0.250	0.05	75.00	0.00	17.00	---	1962	82687
1512 100 MB P	0.25	0.1	1-1	124	0 WATER L10L -200HV	1.000	0.250	0.05	75.00	0.00	20.00	---	1962	82687
1513 100 MB P	0.25	0.1	1-1	124	0 WATER L10L -300HV	1.000	0.250	0.05	75.00	0.00	27.70	---	1962	82687
1514 100 MB P	0.25	0.1	1-1	124	0 WATER L10L 0 AM INCL -300HV	1.000	0.250	0.05	75.00	0.00	20.00	---	1962	82687
1515 100 MB P	0.25	0.1	1-1	124	0 WATER L10L -300HV	1.000	0.250	0.05	75.00	0.00	19.90	---	1962	82687
1516 100 MB P	0.25	0.1	1-1	124	0 WATER L10L -300HV	1.000	0.250	0.05	75.00	0.00	20.00	---	1962	82687
1517 100 MB P	0.25	0.1	1-1	124	0 WATER 0 IN L10L	1.000	0.250	0.05	75.00	0.00	24.00	---	1962	82687
1518 100 MB P	0.25	0.1	1-1	124	0 WATER 0 IN 0 L1003	1.000	0.250	0.05	75.00	0.00	23.20	---	1962	82687
1519 100 MB P	0.25	0.1	1-1	124	0 WATER (1) GLYCERINE (4) L10L	1.000	0.250	0.05	75.00	0.00	24.20	---	1962	82687
1520 100 MB P	0.25	0.1	1-1	124	0 WATER (2, 3) GLYCERINE (2) 3 L10L	1.000	0.250	0.05	75.00	0.00	18.00	---	1962	82687

TABLE 4.16.3.19 (Con't)

CONDITION	PRODUCT FORM	THICK (IN)	TEST TEMP (F)	SPEC OR STR (KSI)	YIELD STRENGTH (KSI)	TITANIUM		TI-BAL-1MD-IV		K (ISCC)	CRACK		MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER		
						ENVIRONMENT		DESIGN			LENGTH						K (ISCC)	K (ISCC)
						W	H	THICK (IN)	DESIGN (IN)		LENGTH (IN)	LENGTH (IN)						
1520F 1HP W9	P	0.25	205	T-L	124.0	WATER	1.000	0.250	DCB	0.985	95.00	42.00*				1962 83609		
1520F 1HP W9	P	0.25	205	T-L	124.0	WATER LICL	1.000	0.250	DCB	0.985	95.00	20.80				1962 83689		
1520F 1HP W9	P	0.25	212	T-L	124.0	SILICONE OIL	1.000	0.250	DCB	0.985	95.00	65.00*				1962 83689		
1520F 1HP W9	P	0.25	205	T-L	124.0	WATER LICL	1.000	0.250	DCB	0.985	95.00	22.70				1962 83689		
1520F 1HP W9	P	0.25	412	T-L	124.0	GLYCERINE LICL	1.000	0.250	DCB	0.985	95.00	26.00				1962 83609		
1450F 1HP AC P 1200F 3HR AC 1000F 2HR AC	P	1.00	R T	T-L	138.9	3.5% NaCl		0.866	CANT			26.40				1981 1R001		
1720F 1HP AC P 1200F 3HR W9	P	1.00	R T	T-S	107.9	3.5% NaCl	1.000	0.500	CANT*		112.00	28.00				1967 70931		
1720F 0.5HR FC P 10 1200F 1200F 0.5HR AC 1200F 3HR ARGIN QUENCH	P	0.25	32	T-L	130.0	WATER 21000PPH CHLORIDE	2.000	0.250	CANT	0.200	65.40	17.70				1973 83855		
1720F 0.5HR FC P 10 1200F 1200F 0.5HR AC 1200F 3HR ARGIN QUENCH	P	0.25	R T	T-L	130.0	WATER 0.1PPH CHLORIDE	2.000	0.250	CANT	0.200	59.50	24.20				1973 85855		
1720F 0.5HR FC P 10 1200F 1200F 0.5HR AC 1200F 3HR ARGIN QUENCH	P	0.25	R T	T-L	150.0	WATER 100PPH CHLORIDE	2.000	0.250	CANT	0.200	58.70	20.80				1973 85855		
1720F 0.5HR FC P 10 1200F 1200F 0.5HR AC 1200F 3HR ARGIN QUENCH	P	0.25	R T	T-L	150.0	WATER 21000PPH CHLORIDE	2.000	0.250	CANT	0.200	67.40	14.00				1973 85855		

*NOTE: DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(KISCC/TYS)SQUARED

TABLE 4.16.3.19 (Con't)

CONDITION	PRODUCT FORM THICK (IN)	TEST SPEC TEMP OR (F)	YIELD STR (KSI)	TITANIUM ENVIRONMENT	TI-RAL-1M0-1V K (ISCC)	SPECIMEN		CRACK LENGTH (IN)	K (ISCC) (RSI*SORT IN)	MEAN DEV	STAN DEV	TEST TIME (MIN)	DATE REFER
						WIDTH (IN) W	THICK (IN) B						
1750 0 5HR FC P TO 1200F, 1200F 0 5HR AC, 1200F 3HR AIR/QUI QUENCH	0.25	R T	T-L	150 0 WATER CHLORIDE	600PPH	2.000	0.250	CANT	0.200	60.30	18.40	-----	1973 05055
1750 0 5HR FC P TO 1200F, 1200F 0 5HR AC, 1200F 3HR AIR/QUI QUENCH	0.25	140	T-L	150 0 WATER CHLORIDE	21000PPH	2.000	0.250	CANT	0.200	62.10	14.70	-----	1973 05055
1750 0 5HR FC P TO 1200F, 1200F 0 5HR AC, 1200F 3HR AIR/QUI QUENCH	0.25	200	T-L	150 0 WATER CHLORIDE	21000PPH	2.000	0.250	CANT	0.200	66.30	19.40	-----	1973 05055
1800F 1HR AC P TO 1200F, 1200F 0 5HR AC, 1200F 3HR AIR/QUI QUENCH	0.60	R T	T-S	120 4 3 5 PCT NACL	1.000	0.500	CANT*	-----	88.00	23.00	-----	-----	1967 70921
2000F 0 5HR AC P TO 1200F, 1200F 0 5HR AC, 1200F 3HR AIR/QUI QUENCH	1.00	R T	T-L	115.1 3 5X NACL	-----	0.866	CANT	-----	-----	47.30	-----	-----	1981 09001

TABLE 4.17.1.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
TITANIUM ALLOY Ti-600/2Fe/2Al AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION	(NUMBER OF SPECIMENS)
		PLATE
CONDITION/HT	L-I	L-I
STA. REAGED AT 1100F 6HR	54.0 ± 1.0 (3)	53.9 ± 1.0 (3)

TABLE 4.17.2.1

CONDITION	TITANIUM										K(IIC) STAN DEV	DATE	REFER
	TI-8M06V2FF3AL K(IIC)												
	FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN (IN)	CRACK LENGTH (IN)	2.9% CRACK (K(IIC)/TVS)±2			
STA. REAGED AT 1100F 6HR	P	1 00	R. T.	L-T	170.0	1.989	0.998	CT	1.001	0.26	53.00	---	86429
		1 00			170.0	1.990	1.002	CT	0.994	0.24	53.10	---	86429
		1 00			170.0	1.995	1.005	CT	0.995	0.29	53.90	54.0/ 1.0	86429
STA. REAGED AT 1100F 6HR	P	1 00	R. T.	T-L	177.0	1.991	0.991	CT	0.987	0.23	53.40	---	86429
		1 00			177.0	1.995	0.998	CT	1.008	0.24	55.00	---	86429
		1 00			177.0	1.993	0.996	CT	1.014	0.23	53.20	53.9/ 1.0	86429
1475F 1.5 HR. 10.1000F 8 HR. AC	E	3 00	R. T.	---	155.0	1.498	0.750	CT	0.747	0.12	34.10	---	1973 87230 (1)
		3 00			155.0	1.500	0.750	CT	0.776	0.14	36.30	---	1973 87230 (1)
		3 00			155.0	1.498	0.750	CT	0.766	0.12	34.30	34.9/ 1.2	1973 87230 (1)

NOTES:
 (1) COMPOSITION (WT PERCENT) 2.26AL, 7.99V, 8.17MO, 0.022C, 0.018M, 0.0070H, 0.160, 0.006CU
 ALPHA PRECIPITATE IN BETA MATRIX
 STRAIGHTNESS OF CRACK FRONT MAY NOT MEET ASTM E399-72 REQUIREMENTS

TABLE 4.18.2.1

TITANIUM 115AL2.55N(EL) K(IC)															
CONDITION	FORM	THICK (IN)	TEMP (F)	SFC	ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5σ (K(IC)/TYS) ^{0.2} (IN)	K(IC) MEAN (KSI*SQRT IN)	K(IC) STAN DEV (KSI*SQRT IN)	DATE	REF
ANNEALED	F	17.00	423	---	---	186.0	2.000	1.006	CT	1.010	0.32	66.30		1970	BB439
						186.0	2.000	1.005	CT	1.060	0.32	66.60		1970	BB439
						186.0	2.000	1.006	CT	1.040	0.27	61.10		1970	BB439
						187.0	2.000	1.000	CT	0.950	0.40	74.50		1970	BB439
ANNEALED	F	17.00	423	N-L	---	187.0	2.000	1.004	CT	1.020	0.34	67.00		1970	BB439
						187.0	2.000	1.000	CT	0.930	0.32	69.30	67.5/ 4.4	1970	BB439
						189.0	2.000	1.000	CT	0.950	0.39	74.50		1970	BB439
						189.0	2.000	1.000	CT	0.910	0.32	67.90		1970	BB439
ANNEALED	F	17.00	423	N-C	---	189.0	2.000	1.000	CT	0.930	0.34	69.30		1970	BB439
						189.0	2.000	1.000	CT	0.930	0.36	71.30	70.8/ 2.9	1970	BB439
						189.0	2.000	1.000	CT	1.040	0.17	49.80		1970	BB439
						189.0	2.000	1.000	CT	1.020	0.19	52.40		1970	BB439
ANNEALED (ES)	F	17.00	423	---	---	186.0	2.000	1.004	CT	1.020	0.36	71.20		1970	BB439 (1)
						186.0	2.000	1.002	CT	1.020	0.35	69.80		1970	BB439 (1)
						186.0	2.000	1.001	CT	1.050	0.35	70.00		1970	BB439 (1)
						186.0	2.000	1.003	CT	1.000	0.35	70.00		1970	BB439 (1)
ANNEALED (ES)	F	17.00	423	---	---	186.0	2.000	1.002	CT	1.010	0.36	70.80		1970	BB439 (1)
						186.0	2.000	1.001	CT	1.010	0.35	69.80	70.3/ 0.6	1970	BB439 (1)
						186.0	2.000	1.000	CT	1.010	0.36	71.20		1970	BB439 (1)
						186.0	2.000	1.001	CT	1.010	0.35	69.80		1970	BB439 (1)
ANNEALED (ES)	F	17.00	423	---	---	186.0	2.000	1.000	CT	1.010	0.36	88.20		1970	BB439 (2)
						186.0	2.000	1.002	CT	1.060	0.44	77.60		1970	BB439 (2)
						186.0	2.000	1.001	CT	1.020	0.30	83.30		1970	BB439 (2)
						186.0	2.000	1.002	CT	1.020	0.37	71.70		1970	BB439 (2)
ANNEALED (ES)	F	17.00	423	---	---	186.0	2.000	1.001	CT	0.990	0.41	75.20	79.2/ 6.6	1970	BB439 (2)
						186.0	2.000	1.001	CT	0.990	0.41	75.20		1970	BB439 (2)

NOTES:
 1) COAXIAL STRUCTURE
 2) INTERMEDIATE STRUCTURE BETWEEN PLATELET ALPHA AND FINE EQUIAxed GRAINS

TABLE 4.19.1.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
TITANIUM ALLOY TIGALANZBN(ELI) AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION		(NUMBER OF SPECIMENS)	
	L-I	I-I	L-I	I-I
1600F 1 HR. WQ. 1050F 4 HR. AC	29.6 ± 0.6 (2)	---	---	8-I
1650F 1 HR. WQ. 1125F 4 HR. AC	34.0 ± 3.9 (2)	---	---	---

TABLE 4.19.2.1

CONDITION	TITANIUM											K (IC) STAN DEV	DATE	REFER
	Ti6Al6V2Sn(ELI) K (IC)													
	PRIMA- RY THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	SPECIMEN THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5° K (IC)/TYS)*2 (IN)	K (IC) (KSI*SQRT IN)	MEAN (IN)			
1600F 1 HR. WQ. 10:00F 4 HR. AC	P	1.00	R T	L-S	179.0	0.477	0.231	NB	0.215	0.10	35.10	1965	04316	
		1.00			179.0	0.479	0.230	NB	0.184	0.07	30.10	1965	04316	
		1.00			179.0	0.477	0.230	NB	0.222	0.08	32.10	1965	04316	
1600F 1 HR. WQ. 10:00F 4 HR. AC	P	1.00	R. T.	L-T	179.0	0.479	0.230	NB	0.177	0.07	30.20	1965	04316	
		1.00			179.0	0.479	0.247	NB	0.223	0.07	29.20	1965	04316	
		1.00			179.0	0.499	0.233	NB	0.200	0.07	30.00	1965	04316	
1650F 1 HR. WQ. 11:25F 4 HR. AC	P	1.00	- 320	L-S	258.0	0.479	0.230	NB	0.221	0.02	24.70	1965	04316	
		1.00			258.0	0.499	0.230	NB	0.206	0.02	22.60	1965	04316	
1550F 1 HR. WQ. 11:25F 4 HR. AC	P	1.00	R. T.	L-S	170.0	0.499	0.230	NB	0.203	0.13	38.60	1965	04316	
		1.00			170.0	0.479	0.230	NB	0.191	0.12	37.50	1965	04316	
1650F 1 HR. WQ. 11:25F 4 HR. AC	P	1.00	R. T.	L-T	170.0	0.499	0.248	NB	0.191	0.09	31.50	1965	04316	
		1.00			170.0	0.499	0.231	NB	0.219	0.11	36.50	1965	04316	

TABLE 4.20

REFERENCES FOR THE TITANIUM ALLOY DATA

- 54304 TI-6AL-4V K_C
 Figge, I. E., "Residual Static Strength of Several Titanium and Stainless Steel Alloys and One Superalloy at - 109 F, 70 F, and 550 F", NASA TN D-2045, Langley Research Center (December 1963).
- 57573 TI-6AL-4V K_C
 Anon., "Fracture Toughness and Tear Tests". Air Force Materials Laboratory, Research and Technology Division, Report No. ML-TDR-64-238 (October 1964).
- 58782 TI-5AL-4V K_C
 Anon., "Thick Section Fracture Toughness", ML-TDR-64-236, Boeing-North American (October 1964).
- 60578 TI-6AL-4V(ELI) K_C
 Christian, J. L., Yang, C. T., and Witzell, W. E., "Physical and Mechanical Properties of Pressure Vessel Materials for Application in a Cryogenic Environment", ASD-TDR-62-258, Part III, General Dynamics/Aeronautics (December 1964).
- 66103 TI-5AL-2.5Sn K_C
 Ferguson, C. W., "Hypervelocity Impact Effects on Liquid Hydrogen Tanks", NASA CR-54852, Douglas Aircraft Co., Inc. (March 1966).
- 66218 TI-5AL-2.5Sn K_C
 Tiffany, C. F., Lorenz, P. M., and Hall, L. R., "Investigation of Plane-Strain Flaw Growth in Thick-Walled Tanks", NASA CR-54837, The Boeing Company (February 1966).
- 67821 TI-8AL-1MO-1V K_C
 Walker, E. K., "A Study of the Influence of Geometry on the Strength of Fatigue Cracked Panels", AFFDL-TR-66-92, Northrop Norair (June 1966).
- 68968 TI-5AL-2.5Sn K_C
 Sullivan, T. L., "Uniaxial and Biaxial Fracture Toughness of Extra-Low-Interstitial 5Al-2.5Sn Titanium Alloy Sheet at 20 K", NASA TN D-4016, Lewis Research Center (June 1967).
- 70733 TI-8AL-1MO-1V K_{Isc}
 Smith, H. R., et al., "A Study of Stress Corrosion Cracking by Wedge-Force Loading", Report D6-19768, The Boeing Company, Renton, Wash., Contract N00014-66-C-0365 (June 1967).
- 70887 TI-6AL-4V K_{Isc}
 TI-6AL-6V-2.5Sn K_{Isc}
 TI-8AL-1MO-1V K_{Isc}
 Peterson, M. H., Brown, B. F., Newbegin, R. L., and Croover, R. E., "Stress Corrosion Cracking of High Strength Steels and Titanium Alloys in Chloride Solutions at Ambient Temperature". Corrosion, 23 (5), 142-148 (May 1967).
- 70931 TI-6AL-4V K_{Isc}
 TI-6AL-4V(ELI) K_{Isc}
 TI-6AL-6V-2.5Sn K_{Isc}
 TI-8AL-1MO-1V K_{Isc}
 Judy, Jr., R. W., and Goode, R. J., "Stress-Corrosion Cracking Characteristics of Titanium in Salt Water", Interim Report 6564, Naval Research Laboratory, Washington, D.C., Contracts NONR-610(09), NONR-760(31) and N00014-66-C0365 (July 21, 1967).

TABLE 4.20 (continued)

71709	TI-8AL-1MO-1V K_{Ic}	Figge, I. E., "Residual-Static-Strength and Slow-Crack-Growth Behavior of Duplex-Annealed TI-8AL-1MO-1V Sheet", NASA TN D-4358, Langley Research Center (March 1968).
74355	TI-6AL-4V K_{Isc}	Stanley, J. K., "Solutions to Some Stress Corrosion Cracking Problems in Aerospace Applications", Technical Report TR-0200 (4112.22)-1, Aerospace Corporation, El Segundo, Calif., Contract F04701-68-C-0200 (November 1968).
75386	TI-4AL-3MO-1V K_{Isc} TI-6AL-4V K_{Isc} TI-8AL-1MO-1V K_{Isc}	Curtis, R. E., et al., "Relationship Between Composition, Microstructure, and Stress Corrosion Cracking (In Salt Solution) In Titanium Alloys", ASM Transactions Quarterly, <u>62</u> (2), 457-469 (June 1969).
75528	TI-6AL-4V K_{Isc}	Bixler, W. D., "Fracture Characteristics of 6Al-4V Titanium Alloy Forgings Containing Alpha Stringer Microstructure", NASA Final Report CR-99512, The Boeing Company, Seattle, Wash., Contract NAS-9-8809 (January 1969).
76411	TI-6AL-4V K_{Ic}	Wessel, E. T., et al., "Engineering Methods for the Design and Selection of Materials Against Fracture", Final Technical Report, Westinghouse Research Laboratories, Pittsburgh, Pa., Contract DA-30-069-AMC-602 (T) (June 24, 1966).
77290	TI-6AL-4V K_{Isc}	Reuter, W. G., et al., "Monitoring of Crack Growth on Ti-6Al-4V Alloy by the Stress Wave Analysis Technique", NASA Report CR-101888, Aerojet General Corporation, Sacramento, Calif. (December 1968).
77456	BETA da/dt , K_{Isc} TI-8AL-1MO-1V da/dt , K_{Isc}	Katz, Y., "Micro-Mechanical Approach to Stress Corrosion Cracking in Titanium Alloys", Thesis Report No. UCRL-19046, University of California, Lawrence Radiation Laboratory, Berkeley, Calif., AEC Contract W-7405-eng-48 (September 1969).
78535	TI-6AL-4V K_{Isc}	Masters, J. N., et al., "Fracture and Nitrogen Tetroxide/Sustained Load Flaw Growth in 6Al-4V Titanium", Final Report D2-121397-1, NASA CR-109366, The Boeing Company, Seattle, Wash., Contract NAS7-100 (October 1969).
80104	TI-5AL-2.5Sn K_{Ic}	Orange, T. W., Sullivan, T. L., and Calfo, F. D., "Fracture of Thin Sections Containing Through and Part-Through Cracks", NASA TN D-6305, Lewis Research Center (April 1971).
80538	TI-6AL-4V K_{Ic}	Petrak, G. J., "Mechanical Property Evaluation of Beta Forged Ti-6Al-4V", Report APHL-TR-70-291, University of Dayton Research Institute, Dayton, Ohio, Contract F33613-69-C-1471 (January 1971).

TABLE 4.20 (continued)

81221	Ti-6Al-4V da/dt. K_{Isc}	Beck, T. R., et al., "Stress Corrosion Cracking of Titanium Alloys: Studies of Cracks in Thin Specimens; SCC of Ti-6Al-4V in Chloride, Iodide and Fluoride Solutions; Stress Corrosion Cracking in Molten Salts; Electrochemistry of Freshly Generated Titanium Surfaces", Report 20, The Boeing Company, Seattle, Wash., Contract NAS 7-489 (June 1971).
81741	Ti-8Al-1Mo-1V da/dt	Bucci, R. J., and Paris, P. C., "Observations on Sustained Load Environmental Crack Growth of a Titanium 8Al-1Mo-1V Alloy", Corrosion, <u>27</u> (12) 525-530 (December 1971).
82651	BETA K_{Isc} BETA III da/dt Ti-8Al-1Mo-1V da/dt	Beck, T. R., and Blackburn, M. J., "Stress Corrosion Cracking of Titanium Alloys: SCC Velocity; Concentration of $TiCl_3$ ", Report 18, The Boeing Company, Seattle, Wash., Contract NAS 7-489 (December 1970).
83222	Ti-6Al-6V-2Sn K_{Ic}	Amateau, M. F., et al., "F-15 Program Final Report Ti-6Al-6V-2Sn and Ti-6Al-4V Fatigue Crack Propagation", Report No. ATR-72(9990)-3, The Aerospace Corporation, El Segundo, Calif. (September 29, 1971).
83689	Ti-8Al-1Mo-1V da/dt. K_{Isc}	Beck, T. R., et al., "Fundamental Investigation of Stress Corrosion Cracking", Report D180-15006-1, The Boeing Company, Aerospace Group, Seattle, Washington, Contract NASW-2245 (April 1962).
83984	Ti-6Al-4V K_c	Peddersen, C. E., and Hylar, W. S., "Fracture and Fatigue-Crack-Propagation Characteristics of $\frac{1}{4}$ -Inch Mill-Annealed Ti-6Al-4V Titanium Alloy Plate", Report G-9706, Battelle, Columbus Laboratories, Columbus, Ohio, Contract N00156-70-C-1336 (November 1, 1971).
84036	Ti-6Al-4V K_{Isc}	Beacham, C. D., and Meyn, D. A., "The Effect of Thickness Upon Sustained Load Crack Propagation in Ti-6Al-4V Alloy Tested in 3% NaCl Solution", NRL Report 7449, Naval Research Laboratory, Washington, D.C. (August 8, 1972).
84282	Ti-6Al-4V K_{Isc}	Spurr, W. F., "SST Technology Follow-On Program, Phase I, Titanium Alloy 6Al-4V Extrusion", Report No. FAA-SS-72-06, Boeing Report D6-60206, The Boeing Company, Commercial Airplane Group, Seattle, Wash., Contract No. DOT-FA-SS-71-12 (July 1972).
84290	Ti-8Al-1Mo-1V da/dt	Smith, H. E., Piper, D. E., and Downey, F. K., "A Study of Stress-Corrosion Cracking by Wedge Force Loading", Engineering Fracture Mechanics, <u>1</u> , p 123-128 (1968), Pergamon Press.

TABLE 4.20 (continued)

84306	TI-6AL-4V K_{Ic} Harrigan, M. J., "B-1 Fracture Mechanics Data for Air Force Handbook Usage", Report TFD-72-501, North American Rockwell, Los Angeles Division, Los Angeles, California (April 21, 1972).
84316	TI-6AL-2Sn K_{Ic} TI-6AL-2Sn(ELI) K_{Ic} DeSisto, T. S., and Hickey, Jr., C. F., "Low-Temperature Mechanical Properties and Fracture Toughness of Ti-6Al-6V-2Sn", ASTM Proceedings, <u>65</u> , 641-653 (1965).
84326	TI-8AL-LMO-1V K_{Isc} Report of NRL Progress, Naval Research Laboratory, Washington, D.C. (May 1968).
84327	TI-8AL-LMO-1V K_{Isc} Report of NRL Progress, Naval Research Laboratory, Washington, D.C. (May 1967).
84328	TI-6AL-4V K_{Isc} Report of NRL Progress, Naval Research Laboratory, Washington, D.C. (November 1968).
84360	TI-6AL-4V K_{Ic} , da/dN , da/dt , K_{Isc} TI-6AL-6V-2Sn K_{Ic} , da/dN TI-6AL-6V-2.5Sn K_{Isc} McDonnell Aircraft Company, McDonnell Douglas Corp., St. Louis, Mo., Phase B Test Program, Report MDC A0913 (May 18, 1971).
85034	TI-6AL-4V K_{Ic} Mitchell, John, "Laboratory Reports on Fracture Toughness Tests", per memo from Ed Cawthorne of February 5, 1973; data sheets from Shultz Steel Company, South Gate, California.
85064	TI-6AL-4V K_{Ic} Bjeletich, J. G., "Development of Engineering Data on Thick-Section Electron-Beam-Welded Titanium", Report N-LJ-71-18, Lockheed Aircraft Corporation, Lockheed Palo Alto Research Laboratory, Palo Alto Calif., Contract F33615-71-C-1338 (October 12, 1972).
85634	TI-6AL-4V K_{Ic} "Fracture Toughness and Tensile Properties Data for Ti-6Al-4V Forgings", Shultz Steel Company, South Gate, Calif., Attached to memo from Ed Cawthorne dated March 5, 1973.
85836	TI-6AL-4V K_{Ic} "B-1 Fracture Toughness Data (K (sub $1c$)) - Rockwell International Corporation, Los Angeles, Calif. (April 24, 1973).
85837	TI-6AL-4V da/dN "Fracture Toughness Data Collection, Rockwell International Corporation, from B-1 Program", Rockwell International Corporation, Los Angeles, Calif. (April 1973).

TABLE 4.20 (continued)

85855	TI-8AL-1MO-1V da/dt, K_{Isc} Boyd, J. D., "Stress-Corrosion Cracking of Ti-8Al-1Mo-1V in Aqueous Environments: 1. The Kinetics of Subcritical Crack Propagation", Metallurgical Transactions, <u>4</u> (4) 1029-1035 (April 1973).
85857	TI-6AL-4V K_{Ic} "Shultz Steel Company - Fracture Toughness Data - May 10, 1973", per memo from Ed Cawthorne of May 10, 1973.
86099	TI-8AL-1MO-1V da/dN Wanhill, R. J. H., "A Review and Analysis of Fatigue Crack Propagation in Titanium Alloys at Room Temperature", Report No. NRL-TR-71033U, National Aerospace Laboratory, The Netherlands (February 1971).
86429	TI-8-8-2-3 K_{Ic} "Fracture Toughness Data", Progress Report on Materials Test Program, General Dynamics Corporation, Fort Worth Division, Fort Worth, Texas, Contract F33615-72-C-2149 (Received July 6, 1973).
86494	TI-6AL-6V-2Sn K_{Ic} Harnsworth, C. L., "Evaluation Report - Fracture Toughness Evaluation of Isothermally Forged Ti-6Al-6V-2Sn STA", Report MXE 72-64, Air Force Materials Laboratory, WPAFB, Ohio (November 15, 1972).
86575	TI-6AL-4V K_{Ic} , K_{Isc} "Rockwell International, B-1 Program, da/dN Data, Center-Cracked Tension Specimens", Lockheed California Company, Burbank, CA, Report LR25152 (Received July 1973) (Memo from Ed Cawthorne dated July 10, 1973).
86688	TI-6AL-4V K_{Ic} , K_{Isc} Snowles, D. O., et al., "Evaluation of Stress-Corrosion Cracking Susceptibility Using Fracture Mechanics Techniques", Final Report, Part I, Aluminum Company of America, Alcoa Technical Center, Alcoa Center, PA, Contract NAS8-21487 (May 31, 1973).
86844	TI-6AL-6V-2Sn da/dN "Crack Growth Rate Data Generated Under USAF Contract F33615-72-C-2165", Lockheed Aircraft Corporation, Lockheed-Georgia Company, Marietta, GA, Contract F33615-72-C-2165, Data sheets received from AFFDL August 13, 1973.
87230	BETA III K_{Ic} TI-6AL-6V-2Sn K_{Ic} TI-8-8-2-3 K_{Ic} DeSisto, T. S., "Fracture Toughness Measurements of Three Titanium Alloy Extrusions", Report AMARC-TR-73-31, Army Materials and Mechanics Research Center, Watertown, MA (July 1973).
88140	TI-6AL-4V da/dN TI-6AL-4V(ELI) da/dN Hall, L. R., Finger, R. W., and Spurr, W. F., "Corrosion Fatigue Crack Growth in Aircraft Structural Materials", Report AFML-TR-73-204, Boeing Aerospace Company, Seattle, WA, Contract AF33615-71-C-1687 (September 1973).

TABLE 4.20 (continued)

88144	BETA III K_{Ic} , da/dN TI-6AL-4V K_{Ic} , da/dt
	Bjeletic, J. G., "Development of Engineering Data on Thick-Section Electron Beam Welded Titanium", Report AFML-TR-73-197, Lockheed Missiles and Space Company, Inc., Palo Alto, CA, Contract F33615-71-C-1338 (August 1973).
88186	TI-6-2-2-2-2 K_{Ic} TI-6AL-6V-2Sn K_{Ic}
	"Selected Pages from Materials Section of Final Report on Cargo/Tanker Phase IA (AFFDL-TR-73-51) and Lockheed Report SMN 378", Summary Report, Lockheed-Georgia Company, Marietta, GA, Contract F33615-72-C-2165 (February 8, 1974).
88439	TI-5AL-2.5Sn(ELI) K_{Ic}
	Reuter, W. G., "Fracture Toughness of Ti-5Al-2.5Sn ELI Forgings at -423 F", Summary Report, Aerojet-General Corporation, Sacramento, CA (September 9, 1970).
88440	TI-6AL-4V K_{Ic}
	"Titanium-6Al-4V Fracture Toughness and Tensile Test Data of December 19, 1973", Memo from E. W. Cawthorne with fracture toughness data from Shultz Steel Company (December 19, 1973).
88468	TI-6AL-4V da/dN
	Bell, P. D., "Data Sheets for Constant Amplitude Crack Growth Data Generated by Grumman Aerospace Corporation for 2219-T851 Aluminum and Mill Annealed 6Al-4V Titanium Alloy Plate", in letter to J. E. Campbell from Grumman Aerospace Corporation, Bethpage, NY, Contract F33615-72-C-1744 (March 15, 1974).
88575	BETAC K_{Ic} , da/dN TI-6AL-4V K_{Ic} , da/dN
	"Advanced Metallic Air Vehicle Structure Program", Material Property Data Test Report Phase II, Report F2M-6148A, General Dynamics, Convair Aerospace Division, Fort Worth, TX, Contract AF33615-73-C-3001 (January 1974).
88579	TI-6AL-4V da/dN
	"B-1 Program da/dN Data for Aluminum Alloys", Rockwell International Corporation, memorandum to H. D. Moran from E. W. Cawthorne, Battelle's Columbus Laboratories (April 3, 1974).
88700	TI-6AL-4V K_{Isc}
	Gilbreath, W. P., and Adamson, M. J., "The Stress Corrosion Susceptibility of Several Alloys in Hydrazine Fuels", NASA Technical Note, Report NASA TN D-7604, Ames Research Center, Moffett Field, CA (February 1974).
88911	TI-5AL-2.5Sn da/dN
	Wanhill, R. J. H., et al., "Fatigue Crack Propagation Data for Titanium Sheet Alloys - Interim Report No. 3:Ti-5Al-2.5Sn", Report NLR TR 72093 U, National Aerospace Laboratory, The Netherlands (July 1972).

TABLE 4.20 (continued)

88962	<p> TI-6AL-4V K_{Ic} TI-6AL-6V-2Sn K_{Ic} TI-6-2-4-6 K_{Ic} </p> <p> Sparks, R. B., and Long, J. R., "Improvement Manufacturing Methods for Producing High Integrity More Reliable Titanium Forgings", Report AFML-TR-73-301, Wyman-Gordon Company, Worcester, MA, Contract AF33615-71-C-1560 (February 1974). </p>
89004	<p> TI-6AL-4V K_{Ic}, K_{Isc} </p> <p> "Rockwell International, B-1 Program Titanium K_{Ic}, K_{Ic}, and K_{Isc} Data for HB-01 Revision", with data attached to memorandum from E. W. Cawthorne to H. D. Moran (May 1, 1974). </p>
89504	<p> TI-6AL-4V K_{Ic} </p> <p> Cervay, R. E., "Mechanical Properties of Ti-6Al-4V Annealed Forgings", Report AFML-TR-74-49, University of Dayton Research Institute, Dayton, OH, Contract F33615-72-C-1282 (March 1974). </p>
90012	<p> TI-6AL-4V K_{Ic} </p> <p> "Ti-6Al-4V Fracture Toughness Data - Shultz Steel Company, South Gate, CA, of August 8, 1974", with memorandum from E. W. Cawthorne to H. D. Moran of Battelle's Columbus Laboratories (August 8, 1974). </p>
90584	<p> TI-6AL-4V K_{Ic} TI-6AL-6V-2Sn K_{Ic} </p> <p> DeMay, S., "Improved Fracture Toughness of Titanium", Final Report, Grumman Aerospace Corporation, Bethpage, NY, Contract N62269-73-C-0127 (June 1973) (AD 778 652). </p>
90589	<p> TI-6AL-6V-2Sn K_{Ic} </p> <p> Fiftal, C. F., and Beck, E. J., "Development of Fracture Mechanics Data for 6Al-6V-2Sn Titanium Alloy", Report MCR-74-43, Martin Marietta Corp., Denver Division, Denver, CO, Contract NAS 9-13599 (January 1974). </p>
90981	<p> TI-6AL-4V da/dN TI-6AL-6V-2Sn K_{Ic}, da/dN </p> <p> Krupp, W. E., Wimmer, F. T., Pettit, D. E., and Hoepfner, D. W., Data Sheets for Final Report on "Investigation of the Effects of Stress and Chemical Environments on the Prediction of Fracture in Aircraft Structural Materials", Rye Canyon Research Laboratory, Lockheed-California Company, Burbank, CA, Contract F33615-71-C-1688, data sheets received October 21, 1974. </p>
91332	<p> TI-6AL-4V da/dN </p> <p> Wells, R. E., "New Alloys for Advanced Metallic Fighter-Wing Structures" Northrop Corporation, Aircraft Division, Hawthorne, Ca, AIAA/ASME/SAE 15th Structures, Structural Dynamics and Materials Conference, Las Vegas, NV (April 17-19, 1974). </p>

TABLE 4.20 (continued)

91793	BETA III K_{Ic}	Van Stone, R. H., Low J. R. Jr., and Shannon, J. L., Jr., "The Effect of Microstructure on the Fracture Toughness of Titanium Alloys", NASA Technical Report No. 2-Ti, Carnegie-Mellon University, Pittsburgh, Pa., and NASA, Lewis Research Center, Cleveland, Ohio, Research Grant NGR 39-087-047 (December 1974).
91945	TI-6AL-6V-2Sn da/dN	Kondas, K. R., et al., "Cyclic-Crack-Growth and Fracture Resistance of Ti-6Al-6V-2Sn as Influenced by Recrystallization Anneal and Interstitial Oxygen Content", NRL Report 7844, Naval Research Laboratory, Washington, D.C. (January 8, 1975).
GD006		Margolis, W. S., "F-16 Material Test Allowables for Aluminum Alloy 7475, 3.0" Plate - T7351 Temper and 0.5" Plate (92" Width) - T7651 Temper and - T7351 Temper", General Dynamics, Fort Worth Division, Report No. 16PR926, April 1978.
GD007	TI-6AL-4V da/dN	Margolis, W. S., "F-16 Material Allowables Evaluating Beta Annealed 6Al-4V Titanium Alloy", General Dynamics, Fort Worth Division, Report No. 16PR944, September 1978.
GE006	TI-6AL-1MO-1V da/dN	"Fatigue Crack Growth Rate Data on Titanium Ti-8-1-1 Alloy Using K_{Ic} Bar Specimens from the TF34 DTA Effort", Data Sent from M. S. Gilbert, General Electric Co., Evendale, Ohio, October 1982.
GE007	TI-6AL-4V da/dN	"Fatigue Crack Growth Rate Data on Titanium Ti-6-4 Alloy Using K_{Ic} Bar Specimens from the TF34 DTA Effort", Data sent from M. S. Gilbert, General Electric Co., Evendale, Ohio, October 1982.
JEM01	TI-6AL-4V K_{Ic} TI-6AL-6V-2Sn K_{Ic}	Yoder, G. R., Cooley, L. A., and Crooker, T. W., "Enhancement of Fatigue Crack Growth and Fracture Resistance in Ti-6Al-4V and Ti-6Al-6V-2Sn Through Micro-Structural Modification", Journal of Engineering Materials and Technology, Vol. 99, pp. 315-318, October 1977.
MA002	TI-6AL-4V K_{Ic} , da/dN TI-6AL-6V-2Sn da/dN	Fracture Toughness of Ti-6Al-4V Plate and Forging, Aluminum 2124-T851 Plate and 7175-T73652 Forging and Fatigue Crack Growth Rate for Ti-6Al-4V Plate and Forging, Ti-6Al-6V-2Sn Extrusion, Aluminum 2124-T851 Plate and Aluminum 7175-T73652 Forging, Data Submitted by D. L. Rich of McDonnell Aircraft Co., St. Louis, MO, Attachment #2, Received March 12, 1982.
MA003	TI-6AL-4V K_{Ic} , da/dN	Seay, S., and Krieg, J. F., "Wing Carry Through Lug Joint Crack Growth Tests", McDonnell Aircraft Co., St. Louis, MO, Report MDC AJ449, Attachment #3, Submitted by D. L. Rich, March 12, 1982.

TABLE 4.20 (continued)

MA005	TI-6AL-4V da/dN, K_{Isc}	Garland, K., and Krieg, J. F., "Final Report - Basic Fracture Data for F-18 Material", McDonnell Aircraft Co., St. Louis, MO, Report No 3 NA-66-7KW, Attachment #5, 1977.
MA006	TI-6AL-4V da/dN	Garland, K., and Krieg, J. F., "Evaluation of the Effect of Material Cyclic Softening and Hardening on Crack Initiation Life and Crack Growth, with and without Overloads, as a Function of Stress Ratio", McDonnell Aircraft Co., St. Louis, MO, April 1978.
MA011	TI-8AL-1MO-1V da/dN	"Final Report, F/RP-4C/D Damage Tolerance and Life Assessment Study - Vol. II", McDonnell Aircraft Co., St. Louis, MO, Contract No. AFSC F33657-73-A-0062, Report No. MDC A2883, February 1975.
NCO01	TI-6AL-4V K_{Ic} TI-6AL-4V(ELI) K_{Ic}	"Plane Strain Fracture Toughness Data Sets on Aluminum, Steel and Titanium Alloys", Data Sent from P. G. Porter of Northrop Corp., Hawthorne, CA, March 1, 1982.
NCO02	TI-6AL-4V da/dN TI-6AL-4V(ELI) da/dN	"Fatigue Crack Growth Rate Data on Aluminum, Steel, and Titanium Alloy", Data sent from P. G. Porter, Northrop Corp., Hawthorne, CA, March 1, 1982.
NLO01	TI-6AL-4V da/dN	Data Sheets on Ti-6Al-4V - Fatigue Crack Growth Rate Tests - submitted by W. S. Johnson, NASA Langley Research Center, Hampton, VA, March 1982.
NRO01	TI-6AL-4V K_{Ic} TI-8AL-1MO-1V K_{Isc}	Yoder, G. R., Cooley, L. A., and Crooker, T. W., "Effects of Microstructure and Frequency on Corrosion-Fatigue Crack Growth in Ti-8Al-1Mo-1V and Ti-6Al-4V", Naval Research Laboratory, Washington, D.C., Report 4678, December 1981.
PW002	TI-6-2-4-2 da/dN TI-8AL-1MO-1V K_{Ic}	Beyer, J. R., Sims, D. L., and Wallace, R. M., "Titanium Damage Tolerant Design Data for Propulsion Systems", United Technologies Corp., Pratt and Whitney Aircraft Group, West Palm Beach, FL, Report AFML-TR-77-101, Contract No. F33615-75-C-5130, June 1977.
PW003	TI-6AL-4V da/dN	Fatigue Crack Growth Rate Data on Titanium and Nickel Base Alloy from B. S. Schwartz, Pratt and Whitney Aircraft Group, Government Products Division, West Palm Beach, FL. July 1982.

TABLE 4.20 (continued)

RI005	CORONA5 K_{Ic} TI-6-2-4-6 K_{Ic} TI-6AL-4V K_{Ic}	Chestnut, J. C., et al., "Fatigue Crack Propagation and Fracture of Titanium Alloys", Rockwell International Science Center, Thousand Oaks, CA, and Department of Metallurgy and Material Science, Carnegie-Mellon University, Pittsburgh, PA.
RI006	TI-6AL-4V K_{Isc}	Ferguson, R. R., and Berryman, R. C., "Fracture Mechanics Evaluation of B-1 Materials", Rockwell International, B-1 Division, Los Angeles, CA, Contract No. F33657-70-C-0800, Report No. AFML-TR-76-137, October 1976.
UD001	TI-6-2-4-6 da/dN	Carvey, R. R., "Ti-6-2-4-6 Elevated Temperature Modeling of Fatigue Crack Growth Rate Data", University of Dayton Research Institute, Dayton, Ohio, Contract No. F33615-80-C-5011 Technical Memorandum UDR-TM-81-48, December 1981.
UD008	TI-6AL-4V K_{Ic} , da/dN	Carvey, R. R., "Beta Processed Titanium 6Al-4V Fracture Properties", University of Dayton Research Institute, Dayton, Ohio, Contract No. F33615-74-C-5024, Technical Memorandum UDRI-TM-75-08, July 1975.
UM001	TI-6AL-4V da/dN	Wilson, D. A., "A Statistically Based Investigation of Microstructural Effect on the Fatigue Properties of Titanium and Titanium Alloys", Dissertation to University of Missouri, in Partial Fulfillment of PhD Requirement, December 1978.